

Ice Behavior under Cyclic Flexural Loading

Andrii Murdza¹, Erland M. Schulson¹, Carl E. Renshaw^{1,2}

¹Thayer School of Engineering, Dartmouth College, Hanover, NH, USA

²Department of Earth Sciences, Dartmouth College, Hanover, NH, USA

ABSTRACT

Recent studies revealed that the flexural strength of S2 columnar-grained laboratory-grown freshwater and saline ice, loaded cyclically across the columns, increases linearly with stress amplitude, in a manner similar for both materials. The studies were conducted over the range of stress amplitudes from 0.1 to 2.6 MPa, frequencies of ~ 0.1 Hz and temperature of -10 °C. The flexure experiments were conducted under reversed 4-point bending. Cyclic strengthening is attributed to the development of an internal back stress that opposes the applied stress and originates possibly from dislocation pileups or grain boundary sliding.

KEY WORDS: Flexural strength; Rheology; Fatigue; Cyclic loading; Ice mechanics

INTRODUCTION

The Arctic and Antarctic floating ice covers and ice shelves are subjected to cyclic loading from ocean swells that can penetrate deeply into an ice pack and potentially result in the breakup of the ice cover (Squire, 2007). A number of instances have been witnessed and described where, under the action of surface waves, a floating cover exhibited sudden breakup into pieces much smaller than the peak wavelength (Shackleton, 1982; Liu and others, 1988; Prinsenberg and Peterson, 2011; Asplin and others, 2012; Collins and others, 2015; Kohout and others, 2016; Hwang and others, 2017). The question arises: what process accounts for sudden failure of the cover? One hypothesis is that the ice may behave similarly to other materials which, when subjected to cyclic loading, fail at stresses below their nominal flexural strength. This type of behavior is called fatigue. As a result, mechanical behavior of ice with a history of repetitive deformations may be different from ice with no thermal-mechanical history. Of the relatively little research that has been performed on the cyclic loading of ice, most of it was done on freshwater ice (Bond and Langhorne, 1997; Cole, 1990; Gupta et al., 1998; Hammond et al., 2018; Haskell et al., 1996; Iliescu et al., 2017; Iliescu and Schulson, 2002; Murdza et al., 2020c, 2021; Nixon and Smith, 1987; Weber and Nixon, 1997); very little work has been done on sea/saline ice. Therefore, we decided to explore and compare the behavior of both freshwater and saline ice under cyclic loading. For this purpose, we conducted cycling experiments in the laboratory. We prepared ice beams, flexed them in a 4-point bending manner and measured the flexural strength. Details of this study are provided below.

EXPERIMENTAL PROCEDURE

We produced the ice in the laboratory through unidirectional solidification of water in an 800 L circular polycarbonate tank in the manner described previously (Golding et al., 2010, 2014; Smith and Schulson, 1993). To grow freshwater columnar-grained S2 ice, tap-water was used. Saltwater columnar S2 ice was produced as follows: the commercial product “Instant Ocean”

was added to tap water to reach a salinity of 17.5 ppt by mass. The salinity of the well-mixed solution was measured using a calibrated YSI Pro30 conductance meter. The solution was then chilled to a temperature $T = 4 \pm 0.5^\circ\text{C}$. To maintain a uniform column diameter, the top of the solution was seeded with ice crystals. Growth was allowed to continue for ~ 7 days using a top-loaded cold plate maintained at $T = -20^\circ\text{C}$. This procedure produced pucks ~ 1 m in diameter and ~ 0.3 m thick.

Thin-section analysis revealed that c-axes of the individual grains of ice in both materials were oriented more or less perpendicular to the long axis of the columnar-shaped grains but randomly oriented within the plane normal to the long axis. The length of the columns exceeded 50 mm; the average column diameter of freshwater and saline ice, respectively, was 5.5 ± 1.3 and 3.8 ± 0.9 mm. Density of freshwater ice was $914.1 \pm 1.6 \text{ kg}\cdot\text{m}^{-3}$ and density of saline ice was $878 \pm 11 \text{ kg}\cdot\text{m}^{-3}$. Melt-water salinity of saline ice was 3.0 ± 0.9 ppt which is similar to the salinity of natural sea ice. Saline ice contained both sub-mm sized brine pockets and supra-mm sized drainage channels. Figure 1 shows the microstructure of both freshwater and saline ice. The microstructure of saline ice is similar to natural first-year sea ice (for comparison, see Figure 3.7 of Schulson and Duval (2009)).

Once grown, the ice was cut into blocks of dimensions $\sim 10 \times 30 \times 20 \text{ cm}^3$, which were stored in a cooler at -10°C . Specimens for flexing were manufactured by milling from the ice blocks thin beams of dimensions $h \sim 16$ mm in thickness (parallel to the long axis of the grains), $b \sim 85$ mm in width, and $l \sim 300$ mm in length. The test specimens were allowed to equilibrate to the test temperature of $-10 \pm 0.5^\circ\text{C}$ for at least 24 hours before testing.

A detailed description of the specimens' preparation and loading can be found elsewhere (Iliescu et al., 2017; Lishman et al., 2020; Murdza et al., 2018, 2019, 2020c, 2020a, 2020d). To summarize: The ice beams were flexed up and down under 4-point loading under constant displacement rate using a servo-hydraulic MTS loading system to which we attached a custom-built 4-point loading frame. A calibrated load cell and a linear variable differential transformer (LVDT) gauge were used for measurements of load and displacement of the upper surface of the ice beam during cycling.

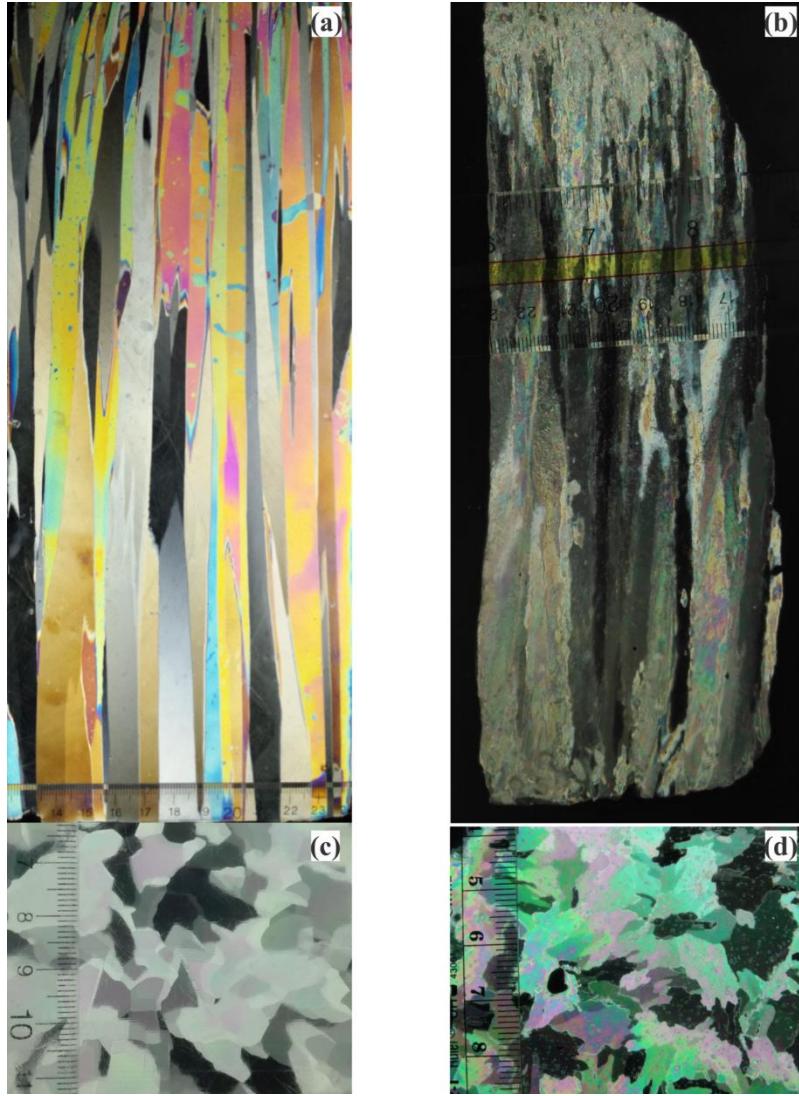


Figure 1. Photographs of a vertically-oriented (a) and a horizontally-oriented (c) thin-sections (~1mm) of columnar-grained freshwater ice as viewed between crossed-polarized filters; photographs of a vertically-oriented (b) and a horizontally-oriented (d) thin-sections of saline ice.

The experiments were performed in a cold room at a temperature of -10°C at an outer-fiber center-point displacement rate of 0.1 mm s⁻¹ (or outer-fiber strain rate of about 1.4 x 10⁻⁴ s⁻¹). This displacement rate resulted in an outer-fiber stress rate of about 1 MPa s⁻¹. The major outer-fiber stress σ_f was calculated from the relationship:

$$\sigma_f = \frac{3PL}{4bh^2} , \quad (1)$$

where P is the applied load and L is the distance between the outer pair of loading cylinders and is set by the geometry of the apparatus to be $L = 254$ mm.

We used two different loading procedures in the present study. Type I loading was a completely reversed stress cycle with constant stress amplitude and mean stress of zero. Type II was similar to Type I but incorporated incremental steps of increasing stress amplitude. This second type of loading essentially consisted of several Type I steps of increasing stress amplitudes. In the

present study we used Type I loading to cycle freshwater ice below stress amplitudes of ~ 1.6 MPa; we used Type I to cycle the saline ice at stresses up to 0.7 MPa. To cycle at stress amplitudes above these values, we first pre-conditioned the specimens through Type II step-loading procedure at progressively higher levels of stress amplitude for ~ 300 cycles at each step. After pre-conditioning, the specimens were cyclically loaded according to Type I loading at least 300 times and generally for ~ 2000 times. Separate experiments revealed that the effect of cycling (described below) saturated after ~ 300 cycles.

RESULTS AND OBSERVATIONS

Flexural strength of non-cycled ice

To establish the strength of the non-cycled ice, we conducted a series of experiments where flexural strength was measured at -10 °C at a nominal outer-fiber center-point displacement rate of 0.1 mm s^{-1} . The average and standard deviation of the measured flexural strength of freshwater and saline ice are 1.67 ± 0.22 and 0.96 ± 0.13 MPa, respectively. These values compare favorably with the values of 1.73 ± 0.25 and 0.85 ± 0.20 MPa reported by Timco and O'Brien (1994) for freshwater ice at temperatures below -4.5 °C and for saline ice of similar salinity.

Flexural strength versus stress amplitude

The experiments performed to investigate the effect of cyclic loading on strength of ice revealed that the flexural strength of both freshwater and saline ice increases with stress amplitude, Figure 2. As already noted, the ice was cycled more than 300 times, often around 2000 times, before being bent to failure. For comparison, we also provide measurements obtained from laboratory tests on S2 lake ice, where ice beams were cycled non-reversely under 3-point loading at -12 °C (Murdza et al., 2020b, 2021). The relationship between the flexural strength, σ_{fc} and cycled stress amplitude, σ_a , appears to be linear for both freshwater and saline ice and can be described by the equation:

$$\sigma_{fc} = \sigma_{f0} + k\sigma_a , \quad (2)$$

where σ_{f0} is the flexural strength of non-cycled ice and k is a constant of value 0.7. Based on Figure 2, freshwater ice is stronger than saline ice; however, it appears that upon cycling, the strength of both freshwater and saline ice increases at about the same rate.

Points on Figure 2 with a cycled stress amplitude above 1.6 MPa in case of freshwater ice and 0.7 MPa in case of saline ice were pre-conditioned through step-cycling Type II at progressively higher stress amplitude levels (see Iliescu and others (2017) for details).

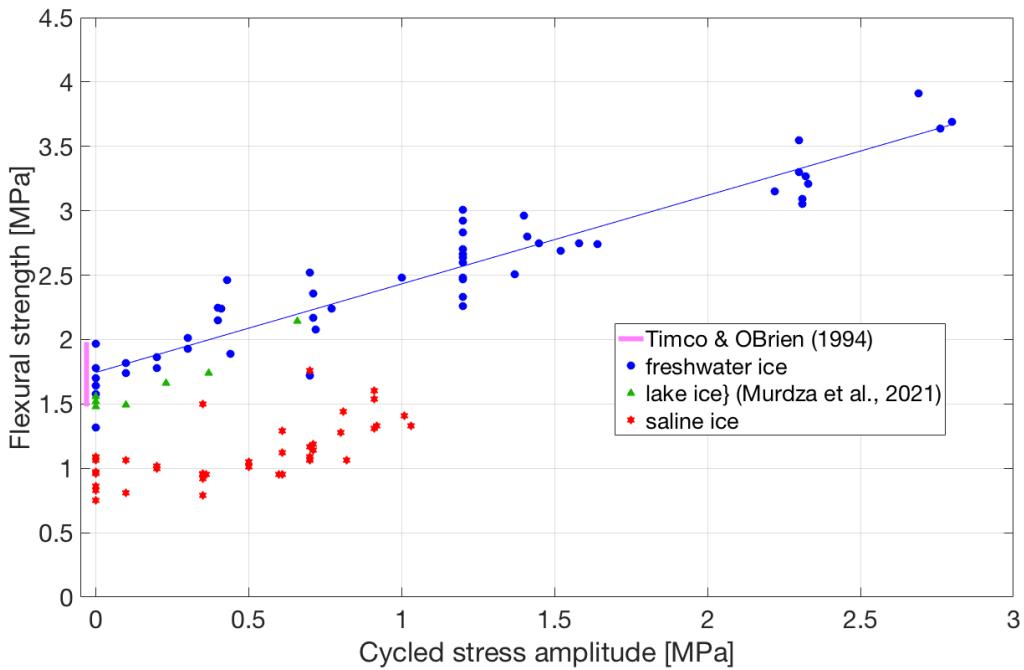


Figure 2. Flexural strength of laboratory-grown freshwater ice and saline ice at -10° C and lake ice at -12° C as a function of cycled stress amplitude, at a mid-point displacement rate of 0.1 mm s⁻¹. During all depicted tests the ice did not fail during cycling but was broken by applying one unidirectional displacement until failure occurred.

Deformation features

It is important to note an absence of remnant microcracks, at least of the size detectable by the unaided eye and optical microscope, in the two parts of freshwater and saline ice beams that were broken after cycling. The implication of this point is noted below.

A second point to note is the absence of recrystallization in cycled and broken freshwater and saline ice. We compared the microstructure of samples before and after cycling and did not find any difference at the level of resolution (~0.1 mm). This suggests that insufficient plastic strain had been imparted to activate this solid-state transformation.

We observed, however, evidence of grain boundary sliding (termed decohesion zones or decohesions). The evidence appeared in the form of whitish features of grain size length upon cycling of freshwater ice. Decohesions were not detected in saline ice specimens upon cycling which is most likely due to the opacity of the material.

Acoustic emissions were not detected in freshwater ice specimens during cycling over the frequency response of 3 kHz–3 MHz and minimum AE amplitude detection threshold of 45 dB during cycling (unlike Cole and Dempsey (2006, 2004); Langhorne and Haskell (1996); Lishman et al. (2020)). We did, however, detect acoustic emissions in saline ice samples during cycling while measuring AE in the same way as in freshwater ice experiments.

DISCUSSION

What is the origin of ice failure in our experiments? Owing to the higher value of compressive strength of ice compared with the tensile strength, failure in ice at bending occurs on a surface that undergoes tensile deformation. Hence, in our work ice strength is always governed by tensile strength. This is consistent if we compare our results on freshwater ice with the results obtained by Carter (1971), who provided measurements on tensile strength of laboratory grown

cylindrical freshwater ice samples. Our flexural strength values, if divided by 1.7 (Ashby and Jones, 2013), are very similar to the Carter's data. Moreover, obtained values of flexural strength of saline ice in the present study, if divided by 1.7, are similar to the values obtained by Richter-Menge and Jones (1993) for the tensile strength of columnar-grained first-year sea ice of 4.1 ± 0.3 ppt salinity loaded uniaxially across the columns at a temperature of -10°C and strain rates of 10^{-5} and 10^{-3} s^{-1} .

Given that the grain size (i.e., column diameter) of the specimens used in the present study is relatively large (\sim a few millimeters) and given the absence of remnant microcracks in broken parts of ice specimens after cycling and failure, we conclude that crack nucleation governs the failure strength and nucleation of the first crack is followed by immediate propagation and creation of the fracture surface. According to Schulson and Duval (2009), either pile-ups of dislocations against other boundaries or grain boundary sliding may be responsible for the nucleation of cracks in ice under crack nucleation regime. Both processes lead to concentrations of stress high enough to overcome the surface energy obstacle to crack nucleation.

The behavior of both freshwater and saline ice under cyclic loading is essentially the same, as suggested by Figure 2, i.e. flexural strength increases at about the same rate. Hence, it is reasonable to assume that the strengthening mechanism for the freshwater and saline ice is similar. However, we should note that there is a possibility of a different strengthening mechanism for saline ice. The prolific flaw structure in saline ice allows for damage accumulation due to a great number of microcracks in regions of microstructural weakness. For example, the brine drainage channels in the test specimens constitute regions of high porosity and thus provide favorable sites for the concentration of such damage. Due to the inherent weakness of the saline ice microstructure, the microstructural stress relief may occur through localized damage via microcracking which may be associated with the acoustic emissions detected in saline ice during cycling. However, the origin of the acoustic emissions during cycling of saline ice could also be explained by a water-hammer effect in which brine entrapped within pockets impacts the wall, first in one direction and then another (discussed in more details in Murdza et al. (2020a)). We refrain, therefore, from further speculation on this point as more research is needed.

SUMMARY

From systematic experiments on the flexural strength of sub-meter sized beams of S2 columnar-grained freshwater and saline ice stressed principally across the columns through reversed cyclic loading at a temperature of -10°C and outer-fiber strain rate of about $1.4 \times 10^{-4}\text{ s}^{-1}$, it is concluded that:

- (i) The flexural strength of ice subsequent to cycling appears to scale linearly with the amplitude of the outer-fiber stress for both freshwater and saline ice.
- (ii) Crack growth is not a significant contribution to the fatigue life of both freshwater and saline ice.
- (iii) Cycling induced grain-boundary sliding occurs in freshwater ice.
- (iv) Cyclic strengthening is attributed to the development of an internal stress that opposes the applied stress and thus raises the level of the applied stress that is required to nucleate a crack.
- (v) The increase in flexural strength of freshwater ice and saline ice attributable to pre-failure load cycling is roughly equivalent.

ACKNOWLEDGEMENTS

We acknowledge helpful discussions/communications with Prof. Harold Frost, Dr. Robert Gagnon, and Dr. Daniel Iliescu. This work was supported by the US Department of the Interior-Bureau of Safety and Environmental Enforcement (BSEE), contract no. E16PC00005 and by National Science Foundation (FAIN 1947-107).

REFERENCES

Ashby, M. F. and Jones, D. R. H.: Engineering materials 2 : an introduction to microstructures and processing, Elsevier/Butterworth-Heinemann, Oxford., 2013.

Asplin, M. G., Galley, R., Barber, D. G. and Prinsenberg, S.: Fracture of summer perennial sea ice by ocean swell as a result of Arctic storms, *J. Geophys. Res. Ocean.*, 117(6), 1–12, doi:10.1029/2011JC007221, 2012.

Bond, P. E. and Langhorne, P. J.: Fatigue behavior of cantilever beams of saline ice, *J. Cold Reg. Eng.*, 11(2), 99–112, doi:10.1061/(ASCE)0887-381X(1997)11:2(99), 1997.

Carter, D.: Lois et mechanisms de l'apparente fracture fragile de la glace de riviere et de lac, PhD Thesis, University of Laval., 1971.

Cole, D. and Dempsey, J.: Laboratory observations of acoustic emissions from antarctic first-year sea ice cores under cyclic loading, in 18th International POAC Conference, p. Vol 3, 1083-1092., 2006.

Cole, D. M.: Reversed direct-stress testing of ice: Initial experimental results and analysis, *Cold Reg. Sci. Technol.*, 18(3), 303–321, doi:10.1016/0165-232X(90)90027-T, 1990.

Cole, D. M. and Dempsey, J. P.: In situ Sea Ice Experiments in McMurdo Sound: Cyclic Loading, Fracture, and Acoustic Emissions, *J. Cold Reg. Eng.*, 18(4), 155–174, doi:10.1061/(ASCE)0887-381X(2004)18:4(155), 2004.

Collins, C. O., Rogers, W. E., Marchenko, A. and Babanin, A. V.: In situ measurements of an energetic wave event in the Arctic marginal ice zone, *Geophys. Res. Lett.*, 42(6), 1863–1870, doi:10.1002/2015GL063063, 2015.

Golding, N., Schulson, E. M. and Renshaw, C. E.: Shear faulting and localized heating in ice: The influence of confinement, *Acta Mater.*, 58, 5043–5056, doi:10.1016/j.actamat.2010.05.040, 2010.

Golding, N., Snyder, S. A., Schulson, E. M. and Renshaw, C. E.: Plastic faulting in saltwater ice, *J. Glaciol.*, 60(221), 447–452, doi:10.3189/2014JoG13J178, 2014.

Gupta, V., Bergström, J. and Picu, C. R.: Effect of step-loading history and related grain-boundary fatigue in freshwater columnar ice in the brittle deformation regime, *Philos. Mag. Lett.*, 77(5), 241–247, doi:10.1080/095008398178372, 1998.

Hammond, N. P., Barr, A. C., Cooper, R. F., Caswell, T. E. and Hirth, G.: Experimental Constraints on the Fatigue of Icy Satellite Lithospheres by Tidal Forces, *J. Geophys. Res. Planets*, 123(2), 390–404, doi:10.1002/2017JE005464, 2018.

Haskell, T. G., Robinson, W. H. and Langhorne, P. J.: Preliminary results from fatigue tests on in situ sea ice beams, *Cold Reg. Sci. Technol.*, 24(2), 167–176, doi:10.1016/0165-

232X(95)00015-4, 1996.

Hwang, B., Wilkinson, J., Maksym, E., Gruber, H. C., Schweiger, A., Horvat, C., Perovich, D. K., Arntsen, A. E., Stanton, T. P., Ren, J. and Wadhams, P.: Winter-to-summer transition of Arctic sea ice breakup and floe size distribution in the Beaufort Sea, *Elem Sci Anth*, 5, 40, doi:10.1525/elementa.232, 2017.

Iliescu, D. and Schulson, E. M.: Brittle compressive failure of ice: Monotonic versus cyclic loading, *Acta Mater.*, 50(8), 2163–2172, doi:10.1016/S1359-6454(02)00060-5, 2002.

Iliescu, D., Murdza, A., Schulson, E. M. and Renshaw, C. E.: Strengthening ice through cyclic loading, *J. Glaciol.*, 63(240), 663–669, doi:10.1017/jog.2017.32, 2017.

Kohout, A. L., Williams, M. J. M., Toyota, T., Lieser, J. and Hutchings, J.: In situ observations of wave-induced sea ice breakup, *Deep. Res. Part II Top. Stud. Oceanogr.*, 131, 22–27, doi:10.1016/j.dsr2.2015.06.010, 2016.

Langhorne, P. J. and Haskell, T. G.: Acoustic emission during fatigue experiments on first year sea ice, *Cold Reg. Sci. Technol.*, 24(3), 237–250, doi:10.1016/0165-232X(95)00021-3, 1996.

Lishman, B., Marchenko, A., Sammonds, P. and Murdza, A.: Acoustic emissions from in situ compression and indentation experiments on sea ice, *Cold Reg. Sci. Technol.*, 172, 102987, doi:10.1016/j.coldregions.2019.102987, 2020.

Liu, A. K., Mollo-Christensen, E., Liu, A. K. and Mollo-Christensen, E.: Wave Propagation in a Solid Ice Pack, *J. Phys. Oceanogr.*, 18, 1702–1712, doi:10.1175/1520-0485(1988)018<1702:WPIASI>2.0.CO;2, 1988.

Murdza, A., Schulson, E. M. and Renshaw, C. E.: Hysteretic behavior of freshwater ice under cyclic loading : preliminary results, in 24th IAHR International Symposium on Ice, pp. 185–192, Vladivostok., 2018.

Murdza, A., Schulson, E. M. and Renshaw, C. E.: The effect of cyclic loading on the flexural strength of columnar freshwater ice, in Proceedings of the International Conference on Port and Ocean Engineering under Arctic Conditions, POAC, vol. 2019-June., 2019.

Murdza, A., Schulson, E. and Renshaw, C.: Behavior of Saline Ice under Cyclic Flexural Loading, *Cryosph. Discuss.*, 1–22, doi:10.5194/tc-2020-300, 2020a.

Murdza, A., Marchenko, A., Schulson, E., Renshaw, C., Sakharov, A., Karulin, E. and Chistyakov, P.: Results of preliminary cyclic loading experiments on natural lake ice and sea ice, in 25th IAHR International Symposium on Ice, pp. 1–10, Trondheim, Norway., 2020b.

Murdza, A., Schulson, E. M. and Renshaw, C. E.: Strengthening of columnar-grained freshwater ice through cyclic flexural loading, *J. Glaciol.*, 66(258), 556–566, doi:10.1017/jog.2020.31, 2020c.

Murdza, A., Polojärvi, A., Schulson, E. M. and Renshaw, C. E.: The flexural strength of bonded ice, *Cryosph. Discuss.*, 1–20, doi:10.5194/tc-2020-301, 2020d.

Murdza, A., Marchenko, A., Schulson, E. M. and Renshaw, C. E.: Cyclic strengthening of lake ice, *J. Glaciol.*, 67(261), 182–185, doi:10.1017/jog.2020.86, 2021.

Nixon, W. and Smith, R.: The Fatigue Behavior of Freshwater Ice, *J. Phys. Colloq.*, 48(C1), 329–335, doi:10.1051/jphyscol:1987146, 1987.

Prinsenberg, S. J. and Peterson, I. K.: Observing regional-scale pack-ice decay processes with helicopter-borne sensors and moored upward-looking sonars, *Ann. Glaciol.*, 52(57), 35–42,

doi:10.3189/172756411795931688, 2011.

Richter-Menge, J. A. and Jones, K. F.: The tensile strength of first-year sea ice, *J. Glaciol.*, 39(133), 609–618, doi:10.3189/S0022143000016506, 1993.

Schulson, E. M. and Duval, P.: *Creep and Fracture of Ice*, Cambridge University Press, Cambridge., 2009.

Shackleton, E. H.: *South: The Story of Shackleton's Last Expedition, 1914–17*, Macmillian, USA., 1982.

Smith, T. R. and Schulson, E. M.: The brittle compressive failure of fresh-water columnar ice under biaxial loading, *Acta Metall. Mater.*, 41(1), 153–163, doi:10.1016/0956-7151(93)90347-U, 1993.

Squire, V. A.: Of ocean waves and sea-ice revisited, *Cold Reg. Sci. Technol.*, 49(2), 110–133, doi:10.1016/j.coldregions.2007.04.007, 2007.

Timco, G. W. and O'Brien, S.: Flexural strength equation for sea ice, *Cold Reg. Sci. Technol.*, 22(3), 285–298, doi:10.1016/0165-232X(94)90006-X, 1994.

Weber, L. J. and Nixon, W. A.: Fatigue of freshwater ice, *Cold Reg. Sci. Technol.*, 26(2), 153–164, doi:10.1016/S0165-232X(97)00014-1, 1997.