

Lightweight Mechanical Metamaterials with Tunable Negative Thermal Expansion

Qiming Wang^{1*}, Julie A. Jackson², Qi Ge^{3,4}, Jonathan B. Hopkins⁵, Christopher M. Spadaccini², Nicholas X. Fang^{3*}

¹ Sonny Astani Department of Civil and Environmental Engineering, University of Southern California, Los Angeles, CA 90089, USA. ² Lawrence Livermore National Laboratory, Livermore, CA 94550, USA. ³ Department of Mechanical Engineering, Massachusetts Institute of Technology, Cambridge, MA 02139, USA. ⁴ Digital Manufacturing and Design Centre, Singapore University of Technology and Design, 487372, Singapore. ⁵ Department of Mechanical and Aerospace Engineering, University of California, Los Angeles, Los Angeles, CA 90095, USA.

Abstract

Ice floating on water is a great manifestation of negative thermal expansion (NTE) in nature. The limited examples of natural materials possessing NTE have stimulated research on engineered structures. Previous studies on NTE structures were mostly focused on theoretical design with limited experimental demonstration in 2D planar geometries. In this work, aided with multimaterial projection micro-stereolithography, we experimentally fabricate lightweight multimaterial lattices that exhibit significant negative thermal expansion in three directions and over a temperature range of 170 degrees. Such NTE is induced by the structural interaction of material components with distinct thermal expansion coefficients. The NTE can be tuned over a large range by varying the thermal expansion coefficient difference between constituent beams and geometrical arrangements. Our experimental results match qualitatively with a simple scaling law and quantitatively with computational models.

*Email: qimingw@usc.edu (Q.W.), nicfang@mit.edu (N.X.F.)

Published as

Qiming Wang, Julie A. Jackson, Qi Ge, Jonathan B. Hopkins, Christopher M. Spadaccini, Nicholas X. Fang, Lightweight Mechanical Metamaterials with Tunable Negative Thermal Expansion, *Physical Review Letters*, 117, 175901, 2016.

Solid materials usually expand when heated because the rising temperature induces the elongation of inter-atomic bonds that manifests itself as volume expansion at the macroscale. However, a number of exceptional solids contract with raising temperatures, exhibiting negative thermal expansions (NTEs) [1-3]. These solids are especially useful for applications where the mismatch in thermal stress should be carefully managed, such as microchip devices[4], adhesive fillers, dental filling[5], and high precision optical or mechanical devices[4,6] under environment conditions with variable temperatures. The NTE effects of these bulk solids are usually attributed to the thermal-induced geometric rotations of molecular units that lead to effective volume shrinkage [1-3]. And the molecular unit rotations can usually be achieved by atomic interaction or phase transformation within the flexible molecular structures [1-3].

Inspired from the molecular mechanisms of the NTE bulk solids, NTE structures with flexible micro or macro architectures of periodic lattice units have been designed by integrating constituents with varied thermal expansion coefficients (TECs) within single structures.

Structural interactions between these constituents with distinct thermal expansion coefficients trigger parts of the structure to rotate or bend to accommodate their thermal expansion within the internal free space, rather than the external space, inducing global volume contraction. Based on this principle, a number of theoretical designs for NTE structures have been proposed to achieve these effects [7-12]. However, the existing experimental validation of NTE effects by using micro-architected structures has been limited to structures with 2D layouts [13-19], while the experimental realization of 3D negative expansion remains elusive [13,15]. This is primarily due to the difficulty in fabricating 3D composite lattices with multiple material constituents and highly sophisticated geometric connections. In addition, existing NTE structures are built with only limited materials choices so that the NTE cannot be well tuned over a large range of temperatures [13-19].

Here, we demonstrate a method to experimentally fabricate 3D composite lattices with tunable NTEs in all three Cartesian directions. The composite lattice is fabricated with a multimaterial projection stereolithography system that enables joining two distinct beam constituents within one lattice structure. The effective volume contraction is induced by constrained thermal expansion of two types of material constituents with different TECs, thus leading to designed deformation. The NTE can be tuned over a large range of temperature by controlling the TECs of the constituent materials and the 3D geometric layout of the structure. The designed mechanism can not only be experimentally implemented in unit cells, but also be scaled up by layering the unit cells into large volume 3D lattices. The experimentally observed NTEs are consistent with our scaling theory and numerical simulations.

The fabrication of the NTE structures is realized with a photopolymerization-based multimaterial stereolithography system (**Fig. 1a**) [20-22] that extends the capability of previous single-material stereolithography systems [23-29]. Briefly, we use patterned UV/blue light to cure photocurable pre-solutions and manufacture 3D structures layer by layer. We switch different pre-solutions alternatively to enable the manufacturing of multimaterials within a single structure (**Fig. S1, Supplemental Method**). We employ photocurable Poly(ethylene glycol) diacrylate (PEGDA) solutions (molar mass 700, Sigma-Aldrich) doped with varied volume concentrations of copper nanoparticles (50-80 nm, US Research Nanomaterials) as the pre-solutions. The

thermal expansion coefficient of solidified PEGDA is approximately $\alpha_1=1.56 \times 10^{-4} \text{ K}^{-1}$. Due to the low TEC ($\sim 2 \times 10^{-5} \text{ K}^{-1}$) and high bulk modulus ($\sim 100 \text{ GPa}$) of the copper particles, the reinforcement with copper particles within PEGDA solids can significantly knock down the TEC (**Table S1, Supplemental Method, Fig. S2**). For example, the TEC of PEGDA solids reinforced with 5% volume of copper nanoparticles becomes $\alpha_2=5.1 \times 10^{-5} \text{ K}^{-1}$, around one third of PEGDA's TEC. The larger the volume concentration of copper reinforcement, the lower the resulting TEC (**Table S1, Supplemental Method, Fig. S2**). It is noted that the high volume concentration of copper significantly elongates the printing time of each layer and also decreases the bonding force between printed layers. We are able to print PEGDA beams with up to 10% volume copper within a reasonable time scale (~ 6 hours each structure).

We design 3D composite structures in the form of cubic unit cells as shown in **Figs. 1b-d**. The unit cell (**Fig. 1b**) is composed of a copper-reinforced PEGDA beam frame (black, $\alpha_2=4-6.1 \times 10^{-5} \text{ K}^{-1}$) and internal tilted PEGDA beams (green). When heated, the PEGDA beams expand more than the copper-reinforced PEGDA beams, thus causing the reinforced beams around the cubic surfaces to bend inward occupying the internal open spaces. Therefore, the overall occupied volume of the structure becomes smaller exhibiting so called NTE. In the fabricated structure (**Fig. 1c**), the pale yellow PEGDA beams and gray reinforced beams form freely standing unit cell structures with size around 6 mm and beam thickness around 200-500 μm . The additive manufacturing is performed by stacking ~ 200 layers (each material 100 layers) with each layer being $\sim 60 \mu\text{m}$.

The thermal expansion properties of the fabricated composite structures are measured within a glass thermal chamber ($5 \times 5 \times 2 \text{ cm}$) with a controlled temperature measured by a thermometer (variation $\pm 10 \text{ K}$ within the chamber) (**Fig. S3**). We gradually increase the temperature from room temperature and wait 30 min for each step to ensure a stable temperature distribution. We then observe the structure deformation with a camera mounted on the top of the glass chamber. It is noted that the observation can only capture deformations in two planar-directions; however, we can flip the structure to observe the thermal-induced deformation in the other direction.

As the temperature in the chamber is gradually increased, the composite structure first maintains the size during the initial temperature segment (e.g., 300K-350K), and then bends inward to decrease its size monotonically as a temperature of $\sim 521 \text{ K}$ is approached (**Fig. 2a** and **Supplemental Movie S1**). We keep the temperature below 530K because the properties of the material constituents will significantly degrade above 550K. To quantify the results, we define the effective thermal expansion ratio η as the lateral expansion ratio (**Fig. 2a**), namely,

$\eta = (L - L_0) / L_0$, where L_0 and L are the lateral size of the unit cell at the initial and heated states, respectively. We then plot the effective expansion ratio as a function of the temperature in **Fig. 2cd**. The error bar in the effective expansion ratio η comes from the standard deviation of along the three primary Cartesian directions of the unit cells. The thermally induced nonlinear geometrical deformation can be understood within three thermal segments via following logic.

We examine the simplest element of the designed structure shown in **Fig. 3a**. In the initial thermal segment (298-350K), to accommodate the thermal expansion, node B may follow

two different bifurcation paths (**Fig. 3b**): inward (path 1) or outward (path 2). Instinctively, node B is expected to move inward by following path 1 (**Fig. 3bi, ii-iii**), because with increasing temperature beams AC and CF with larger thermal expansion coefficient expands significantly to pull beams BC and BE inward (tap BE used to connect other unit within the lattice). However, from the experimental observation, node B first moves outward a little and then snaps inward by following path 2 (**Fig. 3bi, iv-vi**). The behavior from **Fig. 3bi** to **Fig. 3iv** is because that thermal transport within the copper-reinforced PEGDA beams (AB, CE and BF) is much faster than that within the pure PEGDA beams (AC and CF), and the reinforced beams thermally expand more in the very beginning of the temperature increase. Under this circumstance, beams AC and CF become obstacles to prevent node B from moving inward; therefore, node B can only move outward (**Fig. 3bi-biv**). However, node B only move outward slightly with a very small angle ψ (**Fig. 3biv**) and is then trapped at the position, because once beams AC and CF are fully thermal-expanded, beam BC will be pulled inward and locked.

With increasing temperature (350-400 K), node B is expected to snap through from outside the structure (**Fig. 3biv**) to inside the structure (**Fig. 3bv**). To trigger this snap-through transition, the system needs to overcome an energy barrier because beams AB and BF should first become shorter and then longer. Only under a perturbation with a significant amplitude, can this snap-through transition occur [30]. One possible perturbation can be the thermal-induced buckling of beams AB and BF. Since $\psi \sim 0$, the thermal-induced force within beam AB can be approximated as $\sim \alpha_2 \Delta T E_{AB} A_{AB}$, where ΔT is the temperature increase, α_2 is the thermal expansion coefficient of the reinforced beam, and E_{AB} and A_{AB} are the Young's modulus and cross section area of beam AB, respectively. The critical compressive force for the buckling of beam AB is $\pi^2 E_{AB} I_{AB} / (4L_{AB}^2)$, where the second moment of area $I_{AB} = b_{AB} h_{AB}^3 / 12$, and b_{AB} and h_{AB} are the width and thickness of beam AB, respectively [31]. By equating these two forces, we obtain the critical temperature increase for the buckling of beam AB (of BF), namely the snap-through transition shown in **Fig. 3biv-bv**, as

$$\Delta T_c \sim \frac{\pi^2}{3\alpha_2} \left(\frac{h_{AB}}{L_{AB}} \right)^2 \quad (1)$$

By inputting $h_{AB} \sim 300 \mu\text{m}$, $L_{AB} \sim 4.24 \text{ mm}$ and $\alpha_2 \sim 4 - 6.1 \times 10^{-5} \text{ K}^{-1}$, we estimate the critical temperature increase for the snap-through as 68.5-102.8 K. In The theoretical estimation is roughly consistent with the experimental observation (55-100K in shadow areas in **Fig. 2cd**).

With further increasing temperature (above 400 K, **Fig. 3bv-bvi**), beams AC and CF with larger TEC expands significantly to smoothly pull beams BC and BE inward. To understand this problem in the simplest way, we only consider the thermal expansion without elastic stress response and assume node D is fixed due to the symmetry. The displacement of node C induced by thermal expansion of beam AC is $\sim \alpha_1 \Delta T L_{AC} / \cos \beta$, where α_1 is the thermal expansion coefficient of the PEGDA beam, L_{AC} is the length of beam AC, β is the angle between beam AC and beam BC. The displacement of node A in x direction induced by the thermal expansion of

beam AD is $\sim -\alpha_2 \Delta T L_{AD} / \sqrt{3}$, where L_{AD} is the length of beam AD. The displacement of node E in x direction can thus be approximated as

$$d_E \sim \frac{\alpha_1 \Delta T L_{AC}}{\cos \beta} - \alpha_2 \Delta T \left(L_{BC} + L_{BE} + \frac{L_{AD}}{\sqrt{3}} \right) \quad (2)$$

where L_{BC} and L_{BE} are the length of beam BC and BE, respectively. The effective expansion ratio can be calculated as

$$\eta \sim -\frac{2d_E}{\sqrt{2}L_{AB} + 2L_{BE}} \sim -\sqrt{2}\Delta T \alpha_1 \left(\frac{2}{\sin 2\beta} - \frac{k}{\tan \beta} - \frac{kL_{BE}}{L_{AB}} - \frac{\sqrt{2}}{2} \right) \left(\frac{1}{1 + \frac{\sqrt{2}L_{BE}}{L_{AB}}} \right) \quad (3)$$

where $k = \alpha_2 / \alpha_1$. **Equation 3** is a qualitative scaling of the effective expansion ratio and it does not account for the stress response of the constituent beams. More detailed thermoelastic analysis is given in the **Supplemental Method** [32]. Nevertheless, **Equation 3** may be already sufficient to provide enough insight to design composite structures with large negative thermal expansion.

First, the connector tap beam BE should be set as short as possible to achieve large negative thermal expansion. In the experiments we usually set the BE length to be very small (e.g., $\sqrt{2}L_{BE} \ll L_{AB}$) and fixed in the following discussions. Therefore, **Equation 3** can be reduced as

$$\eta \sim -\sqrt{2}\Delta T \alpha_1 \left(\frac{2}{\sin 2\beta} - \frac{k}{\tan \beta} - \frac{\sqrt{2}}{2} \right) \quad (4)$$

Second, to achieve large value of η , the TEC of beam AC should be as large as possible (α_1 large) and the TEC of the reinforced beams (AB, BC and AD) should be as small as possible (k small). In the experiments, we keep the TEC of the PEGDA beams (α_1) and vary the TEC of reinforced beams (α_2) by doping different volume concentrations of copper nano-particles in the PEGDA. By varying copper volume fraction from 2% to 10%, the TEC of the reinforced beam decreases from $6.1 \times 10^{-5} \text{ K}^{-1}$ to $4.0 \times 10^{-5} \text{ K}^{-1}$ (**Fig. 3c**, **Table S1**), and the effective expansion ratio of the composite unit cell increases accordingly (fabricated unit cells in **Fig. S4** and data in **Fig. 2c**). It is noted that it is not necessary for the higher reinforced concentration to lead to higher effective expansion ratios because the higher reinforced concentration also induces higher rigidity (**Table S1**) which makes the reinforced beams more difficult to deform.

Third, from **Equation 4**, the effective negative thermal expansion ratio increases with increasing angle β (**Fig. S5**). If we fix the length of beam AB, the angle β is controlled by the length of beam BC. Therefore, we fabricate composite structures with varied beam BC length

(**Fig. S6**) and confirm that the negative thermal expansion indeed increases by decreasing BC length from 1.17 mm to 0.74mm (**Fig. 2d**). It is noted that when β is approaching its limits of $\pi/2$ or $\text{atan}(\sqrt{2})$, the interaction between the PEGDA beam AC and reinforced beams AB and AD may have a large volume of overlaps; therefore, around these two limiting values, the effective expansion ratio does not necessarily increase with the angle β .

To further quantitatively understand the structure and validate the experimental results, we perform finite element analyses with measured mechanical properties (**Table S1** and **Figs. 3c and S8**). Since the composite structures are fabricated additively layer by layer (**Fig. S7**), we measure the Young's modulus and thermal expansion coefficient in two orthogonal directions. However, the measured results in two directions differ slightly (**Table S1** and **Fig. S8**). Therefore, we treat the beams in our FEA models as homogeneous linear thermoelastic solids with the effective properties in **Table S1**. By considering the symmetry of the problem, we only analyze 1/8 of the unit cell (**Fig. S9a**) and model it as a three dimensional thermomechanical problem (2D view in **Fig. 2b** and **Supplemental Movie S2**, 3D view in **Fig. S9b** and **Supplemental Movie S3**). Overall, our FEA results approximately agree with the experimental results (**Fig. 2**).

The unit cell design of negative thermal expansion composites can be scaled up to a larger volume lattice. The composite lattices are formed by connecting the middle tabs of unit cells (**Fig. 4a**). When heated, the middle tabs move towards the internal free space of the unit cells, and the corners of two unit cells thus squeeze the gap between the unit cells (**Fig. 4a**). For example, when heated the gap distance may reduce from L_g to $L_g - \Delta L$. Therefore, the overall occupied volume of the lattice decreases with the increasing temperature. To demonstrate the concept, we fabricated 2 by 2 by 2 lattices with PEGDA beams and reinforced beams with 5%vol copper (**Figs. 1e-g**). The lattice indeed exhibits large NTE ($\sim 2.9 \times 10^{-5} \text{ K}^{-1}$) over a large range of temperature (350K-524K) (**Fig. 4bc** and **Supplemental Movie S4**). The NTE coefficient is very close to that of the corresponding unit cells ($\sim 2.96 \times 10^{-5} \text{ K}^{-1}$ in **Fig. 2cd**), confirming that layering unit cells into a large volume lattice does not compromise the overall NTE performance. In addition, the experimental results also agree with the finite element analysis (**Fig. 4b**).

As shown in **Figs. 2cd and 4b**, the effective negative thermal expansion of the unit cell can be tuned over a factor of three, from $-1.57 \times 10^{-5} \text{ K}^{-1}$ to $-4.06 \times 10^{-5} \text{ K}^{-1}$ by varying the copper volume concentration from 2% to 10%, and from $-1.78 \times 10^{-5} \text{ K}^{-1}$ to $-3.85 \times 10^{-5} \text{ K}^{-1}$ by varying the length of beam BC. The negative thermal expansion is in a reasonable range compared with the existing theoretical studies and experimental demonstrations of NTE lattices [7-19]. To the best of our knowledge, the current work is the first experimental demonstration that shows large tunability of negative thermal expansion in three dimensions in microlattice structures. In addition, the negative thermal expansion which exhibits itself over a large range of temperature, i.e., $\sim 350\text{K}$ to $\sim 520\text{K}$, can enable potential applications within an environment with large temperature variations. Moreover, the fabricated lattice (**Fig. 1f**) is highly porous and lightweight with ultralow density ($\sim 0.23 \text{ g/cm}^3$), much smaller than the densities of PEGDA solid (1.13 g/cm^3) and copper-reinforced PEGDA solid (5Vol%, 1.52 g/cm^3).

In summary, we fabricated 3D multimaterial composite lattices consisting of solid beams with distinct TECs resulting in tunable negative thermal expansion. We developed a simple scaling law to qualitatively understand the beam-interaction induced negative thermal expansion. Guided by the scaling law, the NTE of composite unit cells can be tuned by varying the TEC differences and geometrical arrangements. We also demonstrate the unit cells can be tessellated into large volume lattices with significant NTEs. We expect our designs of 3D NTE lattices and experimental fabrication can contribute to a number of potential applications where thermal stress should be carefully managed and materials with minimum or negative thermal expansion can mitigate the thermal damage or improve instrument accuracy over large temperature variations. Specifically, zero-thermal-expansion structures may be realized with our additive manufacturing system, through judiciously offsetting the positive and negative effects within the lattices, or assembling NTE structures with positive-thermal-expansion solids in interdigitated patterns. The low dielectric constant of such composite material would also offer promising applications for printed circuit boards with low losses that can survive high temperature differences. In addition, used thermoplastic PEGDA does not show optimal thermal cyclability and manufacturing with materials with better thermal cyclability can significantly improve the structural durability.

We acknowledge the financial support of the DARPA Materials with Controlled Microstructural Architectures program (Program Manager Dr. Judah Goldwasser). Portions of this work were conducted under the auspices of the U.S. Department of Energy by Lawrence Livermore National Laboratory under contract DE-AC52-07NA27344 (LLNL-JRNL-697779). Q.W. thanks the startup fund from the University of Southern California and NSF grant No. 1649093. N.X.F. acknowledges the financial support by Office of Naval Research, Multidisciplinary University Research Initiative (No. N00014-13-1-0631). Q. G. acknowledges support from SUTD-MIT joint postdoctoral program.

Reference

- [1] K. Takenaka, *Sci. Technol. Adv. Mater.* **13**, 013001 (2012).
- [2] G. D. Barrera, J. A. O. Bruno, T. H. K. Barron, and N. L. Allan, *J. Phys.: Condens. Matter* **17**, R217 (2005).
- [3] W. Miller, C. Smith, D. Mackenzie, and K. Evans, *J. Mater. Sci.* **44**, 5441 (2009).
- [4] C. Closmann, A. Sleight, and J. Haygarth, *J. Solid State Chem.* **139**, 424 (1998).
- [5] A. Versluis, W. H. Douglas, and R. L. Sakaguchi, *Dent. Mater.* **12**, 290 (1996).
- [6] W. J. Clegg and A. Kelly, *Adv. Eng. Mater.* **4**, 388 (2002).
- [7] O. Sigmund and S. Torquato, *Appl. Phys. Lett.* **69**, 3203 (1996).
- [8] R. Lakes, *Appl. Phys. Lett.* **90**, 221905 (2007).
- [9] M. Hirota and Y. Kanno, *Optim. Eng.*, 1 (2015).
- [10] J. Lehman and R. Lakes, *J. Intell. Mater. Syst. Struct.* **23**, 1263 (2012).
- [11] J. Lehman and R. Lakes, *J. Mater. Res.* **28**, 2499 (2013).
- [12] J. B. Hopkins, H. Lee, N. X. Fang, and C. M. Spadaccini, in *ASME 2015 International Design Engineering Technical Conferences and Computers and Information in Engineering Conference* (American Society of Mechanical Engineers, 2015), pp. V02BT03A006.
- [13] A. Takezawa, M. Kobashi, and M. Kitamura, *APL Materials* **3**, 076103 (2015).
- [14] J. Qi and J. W. Halloran, *J. Mater. Sci.* **39**, 4113 (2004).
- [15] C. A. Steeves, S. L. dos Santos e Lucato, M. He, E. Antinucci, J. W. Hutchinson, and A. G. Evans, *J. Mech. Phys. Solids* **55**, 1803 (2007).

- [16] J. Berger, C. Mercer, R. M. McMeeking, and A. G. Evans, *J. Am. Ceram. Soc.* **94**, s42 (2011).
- [17] E. Gdoutos, A. Shapiro, and C. Daraio, *Exp. Mech.* **53**, 1735 (2013).
- [18] C. A. Steeves, C. Mercer, E. Antinucci, M. Y. He, and A. G. Evans, *Int. J. Mech. Mater. Des.* **5** (2009).
- [19] N. Yamamoto, E. Gdoutos, R. Toda, V. White, H. Manohara, and C. Daraio, *Adv. Mater.* **26**, 3076 (2014).
- [20] K. Arcaute, B. Mann, and R. Wicker, *Acta Biomater.* **6**, 1047 (2010).
- [21] J.-W. Choi, H.-C. Kim, and R. Wicker, *J. Mater. Process. Technol.* **211**, 318 (2011).
- [22] C. Zhou, Y. Chen, Z. Yang, and B. Khoshnevis, in *Annual Solid Freeform Fabrication Symposium, Austin, TX2011*.
- [23] X. Zheng, J. Deotte, M. P. Alonso, G. R. Farquar, T. H. Weisgraber, S. Gemberling, H. Lee, N. Fang, and C. M. Spadaccini, *Rev. Sci. Instrum.* **83**, 125001 (2012).
- [24] X. Zheng *et al.*, *Science* **344**, 1373 (2014).
- [25] H. Lee, J. Zhang, H. Jiang, and N. X. Fang, *Phys. Rev. Lett.* **108**, 214304 (2012).
- [26] J. Bauer, S. Hengsbach, I. Tesari, R. Schwaiger, and O. Kraft, *Proc. Nat. Acad. Sci. U.S.A.* **111**, 2453 (2014).
- [27] L. R. Meza, S. Das, and J. R. Greer, *Science* **345**, 1322 (2014).
- [28] J. R. Tumbleston *et al.*, *Science* **347**, 1349 (2015).
- [29] T. A. Schaedler, A. J. Jacobsen, A. Torrents, A. E. Sorensen, J. Lian, J. R. Greer, L. Valdevit, and W. B. Carter, *Science* **334**, 962 (2011).
- [30] J. M. T. Thompson and G. W. Hunt, *Elastic instability phenomena* (Wiley Chichester etc., 1984).
- [31] S. P. Timoshenko and J. M. Gere, *Theory of elastic stability* (Courier Corporation, 2009).
- [32] J. D. Renton, *Elastic Beams and Frames* (Elsevier, 2002).

Figures and captions

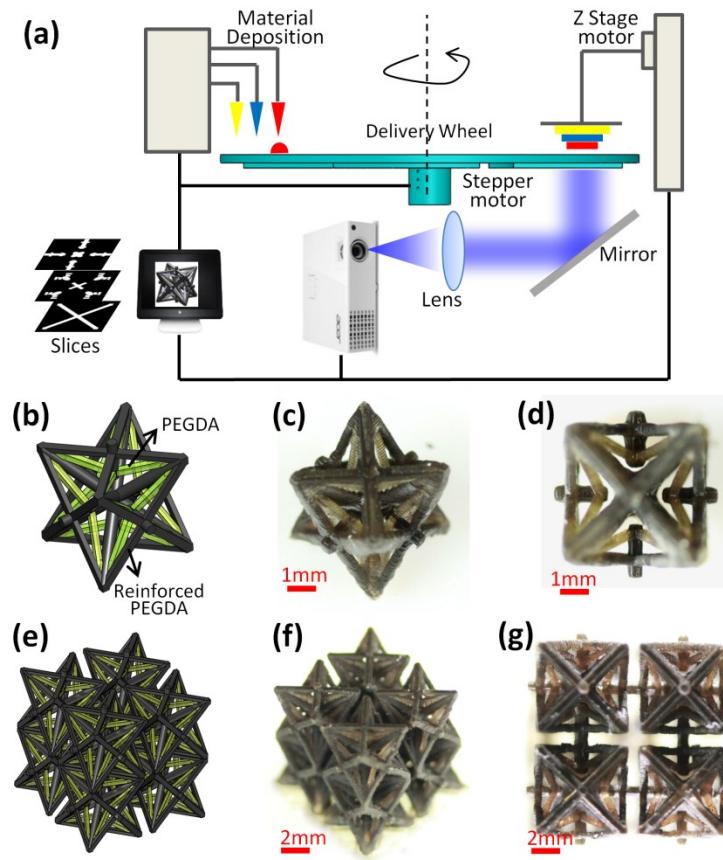


FIG 1. (Color online) (a) Schematic of the multimaterial projection micro-stereolithography system. (b, e) CAD designs and fabricated samples in (c, f) 3D and (d, g) 2D views of the fabricated unit cell and 2 by 2 lattice, respectively.

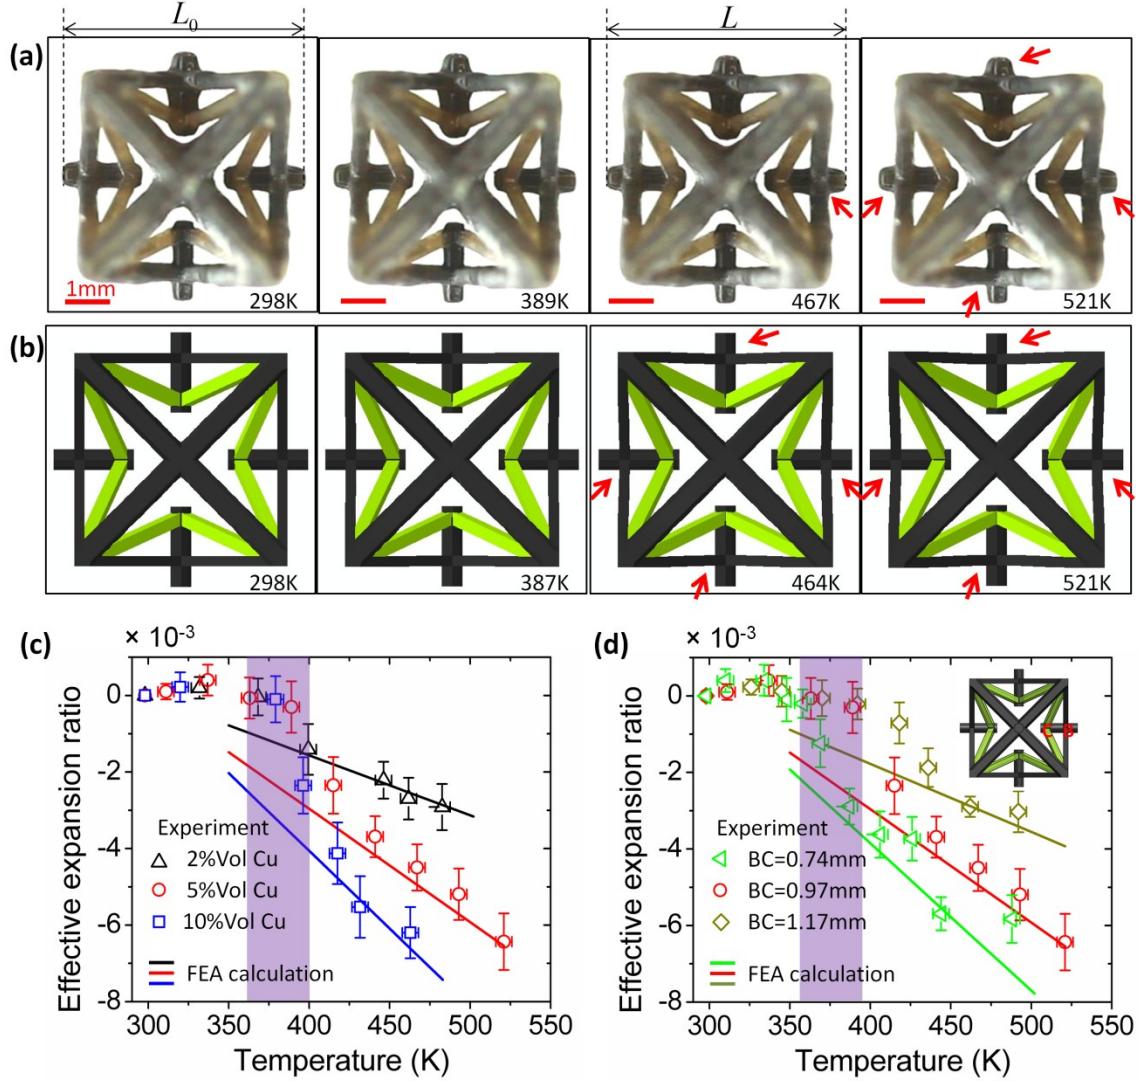


FIG 2. (Color online) (a) Experimental and (d) finite element simulation sequences of a unit cell with increasing temperature. The red arrows indicate the inward bending of the reinforced PEGDA beams. (c-d) Experimentally observed and computationally calculated effective expansion ratios varied with increasing temperatures, (c) with varied volume concentrations of reinforced copper nanoparticles and (d) with varied lengths of beam BC (indicated in the inset of d). The shadow areas in (c-d) show the snap-through temperature range. The FEA-simulated negative thermal expansion coefficients are $-1.57 \times 10^{-5} \text{ K}^{-1}$, $2.91 \times 10^{-5} \text{ K}^{-1}$ and $-4.06 \times 10^{-5} \text{ K}^{-1}$ in (c), $-1.71 \times 10^{-5} \text{ K}^{-1}$, $2.91 \times 10^{-5} \text{ K}^{-1}$ and $-3.93 \times 10^{-5} \text{ K}^{-1}$ in (d), respectively.

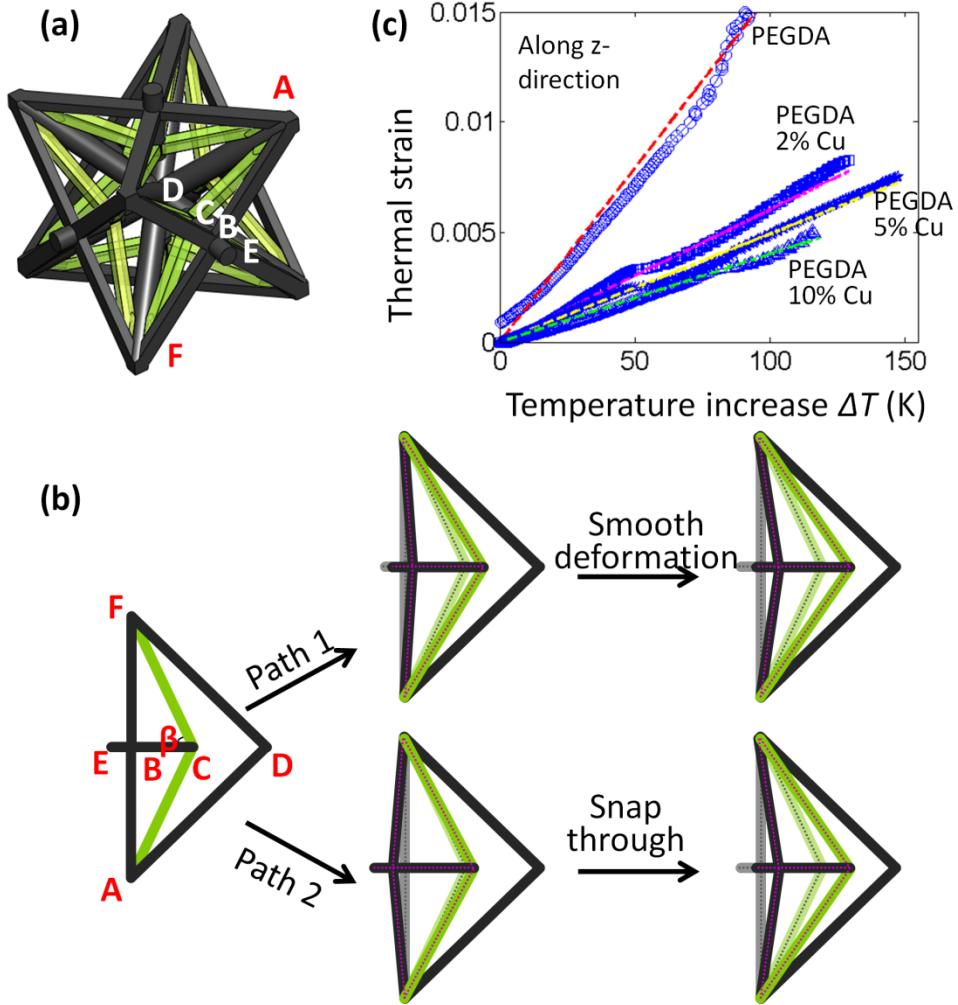


FIG 3. (Color online) (a) A unit cell model to illustrate the key nodes. (b) Two bifurcation deformation paths of the simplest model with key nodes illustrated in (a). In path 1, node B moves inward with increasing temperature. In path 2, node B first moves outward, then snaps through inward, and smoothly moves inward with increasing temperature. (c) The thermal-induced strain in reinforced PEGDA beams with various copper reinforcement fractions in functions of temperature increase.

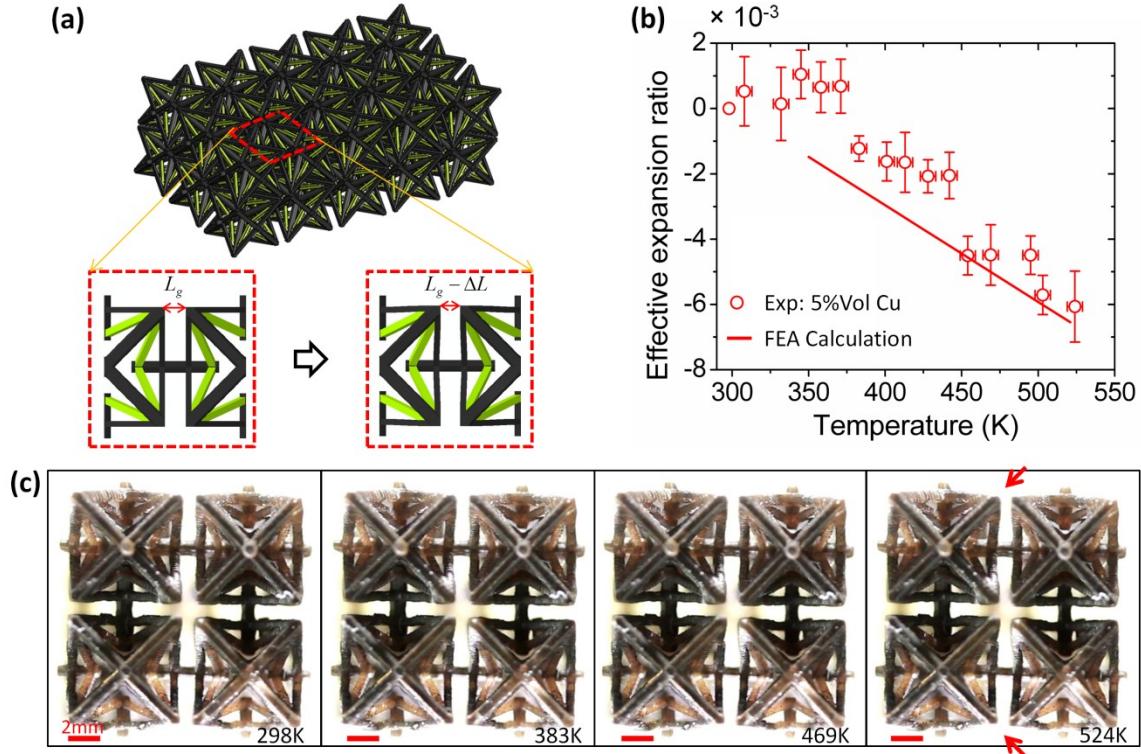


FIG 4. (Color online) (a) A CAD model of a composite lattice by layering a number of unit cells. The inset of (a) shows the deformation mechanism between unit cells within the composite lattice. (b) Experimentally observed and computationally calculated effective expansion ratios and (c) experimental sequences of a 2 by 2 composite lattice under raising temperature. The arrows indicate the deformation.

Supplemental Materials for

Lightweight Mechanical Metamaterials with Tunable Negative Thermal Expansion

Qiming Wang^{1*}, Julie A. Jackson², Qi Ge^{3,4}, Jonathan B. Hopkins⁵, Christopher M. Spadaccini², Nicholas X. Fang^{3*}

¹ Sonny Astani Department of Civil and Environmental Engineering, University of Southern California, Los Angeles, CA 90089, USA. ² Lawrence Livermore National Laboratory, Livermore, CA 94550, USA. ³ Department of Mechanical Engineering, Massachusetts Institute of Technology, Cambridge, MA 02139, USA. ⁴ Digital Manufacturing and Design Centre, Singapore University of Technology and Design, 487372, Singapore. ⁵ Department of Mechanical and Aerospace Engineering, University of California, Los Angeles, Los Angeles, CA 90095, USA.

*Email: qimingw@usc.edu (Q.W.), nicfang@mit.edu (N.X.F.)

1. Supplemental Method

1.1. Fabrication of multi-material lattices

The fabrication of the NTE structures is realized with a photopolymerization-based multimaterial stereolithography system [1-3] that extends the fabrication capability of previous single-material stereolithography systems [4-10]. In a typical fabrication process (**Fig. 1a**), a 3D CAD model is first sliced into a series of images with a prescribed spacing along the vertical direction. These 2D sliced images are transmitted to a spatial light modulator (SLM) and illuminated with UV/blue light from a light emitting diode. Each image is sequentially projected onto the surface of a photocurable pre-solution that includes copper nanoparticles (50-80 nm, US research nanomaterials) with varied volume fractions, 0.03-0.2 wt% surfactant disodium edetate (Sigma Aldrich) and PEGDA (average molar mass 700, Sigma-Aldrich). The exposed solution is solidified, forming a layered structure on a printing stage. As the printing stage is lifted off, another material solution drop can be delivered beneath the stage by a rotational wheel (**Fig. S1**). By lowering the stage by a prescribed height and illuminating the polymer solution with another sliced image, a second material layer can be printed on the structures. By repeating these processes, we can print multimaterial structures with arbitrary 3D geometries. To eliminate the contamination between different polymer pre-solutions, we wash the structures within an ethanol bath after every layer and then absorb the ethanol residues with cotton pads (**Fig. S1**).

1.2. Thermal expansion coefficient of Cu-PEGDA nanocomposite

The thermal expansion coefficients of Cu-PEGDA nanocomposite can be approximated as [11],

$$\alpha_2 \approx \frac{\phi_c K_c \alpha_c + (1 - \phi_c) K_1 \alpha_1}{\phi_c K_c + (1 - \phi_c) K_1} \quad (S1)$$

Where ϕ_c , K_c and α_c are volume fraction, bulk modulus and thermal coefficient of copper particle, respectively. K_1 and α_1 are bulk modulus and thermal coefficient of PEGDA, respectively. Here we estimate that $K_c \sim 100 \times 10^9$ pa, $\alpha_c \sim 2 \times 10^{-5}$ K⁻¹, $\alpha_1 \sim 1.56 \times 10^{-4}$ K⁻¹ and $K_1 \sim 600 \times 10^6$ Pa. As shown in the **Fig. S2**, due to the high bulk modulus of the copper particles, the thermal expansion coefficient initially decreases dramatically with increasing particle volume fractions, but saturates for high volume fractions. The experimental results approximately agree with the theoretical predictions.

1.3. Thermoelastic analysis of the lattice structure

Here we present an analytical model to understand the thermomechanical deformation of a unit cell (**Fig. 3a**). The analyzed model is shown in **Fig. 3a**.

We first consider a planar beam as shown in **Fig. S9a**. The node t is loaded with horizontal force F_{xt} , vertical force F_{yt} and bending momentum M_t , accompanied with displacement δ_{xt} and δ_{yt} and rotation angle θ_t . Similarly, the node s is loaded with force F_{xs} and F_{ys} and bending momentum M_s , accompanied with displacement δ_{xs} and δ_{ys} and rotation angle θ_s . We further denote l as the length, A the cross section area, I the area inertia and E Young's modulus. The loading and the response can be related by structural matrix as the following[12],

$$\begin{bmatrix} F_{xs} \\ F_{ys} \\ M_s \end{bmatrix} = \begin{bmatrix} \frac{EA}{l} & 0 & 0 \\ 0 & \frac{12EI}{l^3} & \frac{6EI}{l^2} \\ 0 & \frac{6EI}{l^2} & \frac{4EI}{l} \end{bmatrix} \begin{bmatrix} \delta_{xs} \\ \delta_{ys} \\ \theta_s \end{bmatrix} + \begin{bmatrix} -\frac{EA}{l} & 0 & 0 \\ 0 & -\frac{12EI}{l^3} & \frac{6EI}{l^2} \\ 0 & -\frac{6EI}{l^2} & \frac{2EI}{l} \end{bmatrix} \begin{bmatrix} \delta_{xt} \\ \delta_{yt} \\ \theta_t \end{bmatrix} \quad (S1)$$

$$\begin{bmatrix} F_{xt} \\ F_{yt} \\ M_t \end{bmatrix} = \begin{bmatrix} -\frac{EA}{l} & 0 & 0 \\ 0 & -\frac{12EI}{l^3} & -\frac{6EI}{l^2} \\ 0 & \frac{6EI}{l^2} & \frac{2EI}{l} \end{bmatrix} \begin{bmatrix} \delta_{xs} \\ \delta_{ys} \\ \theta_s \end{bmatrix} + \begin{bmatrix} \frac{EA}{l} & 0 & 0 \\ 0 & \frac{12EI}{l^3} & -\frac{6EI}{l^2} \\ 0 & -\frac{6EI}{l^2} & \frac{4EI}{l} \end{bmatrix} \begin{bmatrix} \delta_{xt} \\ \delta_{yt} \\ \theta_t \end{bmatrix} \quad (S2)$$

When the beam is tilted by an angel ξ (**Fig. S8b**), the structural matrix can be expressed by a coordinate transformation[12], i.e.,

$$[K]_{tilted} = \begin{bmatrix} \cos \xi & -\sin \xi & 0 \\ \sin \xi & \cos \xi & 0 \\ 0 & 0 & 1 \end{bmatrix} [K] \begin{bmatrix} \cos \xi & \sin \xi & 0 \\ -\sin \xi & \cos \xi & 0 \\ 0 & 0 & 1 \end{bmatrix} \quad (S3)$$

With the coordinate transformation in **Eq. S3**, the new matrix equations can be written as

$$\begin{bmatrix} F_{xs} \\ F_{ys} \\ M_s \end{bmatrix} = \begin{bmatrix} \frac{EA}{l} \cos^2 \xi + \frac{12EI}{l^3} \sin^2 \xi & \sin \xi \cos \xi \left(\frac{EA}{l} - \frac{12EI}{l^3} \right) & -\frac{6EI}{l^2} \sin \xi \\ \sin \xi \cos \xi \left(\frac{EA}{l} - \frac{12EI}{l^3} \right) & \frac{EA}{l} \sin^2 \xi + \frac{12EI}{l^3} \cos^2 \xi & \frac{6EI}{l^2} \cos \beta \\ -\frac{6EI}{l^2} \sin \xi & \frac{6EI}{l^2} \cos \xi & \frac{4EI}{l} \end{bmatrix} \begin{bmatrix} \delta_{xs} \\ \delta_{ys} \\ \theta_s \end{bmatrix} \quad (S4)$$

$$+ \begin{bmatrix} -\frac{EA}{l} \cos^2 \xi - \frac{12EI}{l^3} \sin^2 \xi & \sin \xi \cos \xi \left(-\frac{EA}{l} + \frac{12EI}{l^3} \right) & -\frac{6EI}{l^2} \sin \xi \\ \sin \xi \cos \xi \left(-\frac{EA}{l} + \frac{12EI}{l^3} \right) & -\frac{EA}{l} \sin^2 \xi - \frac{12EI}{l^3} \cos^2 \xi & \frac{6EI}{l^2} \cos \xi \\ \frac{6EI}{l^2} \sin \xi & -\frac{6EI}{l^2} \cos \xi & \frac{2EI}{l} \end{bmatrix} \begin{bmatrix} \delta_{xt} \\ \delta_{yt} \\ \theta_t \end{bmatrix}$$

$$\begin{bmatrix} F_{xt} \\ F_{yt} \\ M_t \end{bmatrix} = \begin{bmatrix} -\frac{EA}{l} \cos^2 \xi - \frac{12EI}{l^3} \sin^2 \xi & \sin \xi \cos \xi \left(-\frac{EA}{l} + \frac{12EI}{l^3} \right) & \frac{6EI}{l^2} \sin \xi \\ \sin \xi \cos \xi \left(-\frac{EA}{l} + \frac{12EI}{l^3} \right) & -\frac{EA}{l} \sin^2 \xi - \frac{12EI}{l^3} \cos^2 \xi & -\frac{6EI}{l^2} \cos \xi \\ -\frac{6EI}{l^2} \sin \xi & \frac{6EI}{l^2} \cos \xi & \frac{2EI}{l} \end{bmatrix} \begin{bmatrix} \delta_{xs} \\ \delta_{ys} \\ \theta_s \end{bmatrix} \quad (S5)$$

$$+ \begin{bmatrix} \frac{EA}{l} \cos^2 \xi + \frac{12EI}{l^3} \sin^2 \xi & \sin \xi \cos \xi \left(\frac{EA}{l} - \frac{12EI}{l^3} \right) & \frac{6EI}{l^2} \sin \xi \\ \sin \xi \cos \xi \left(\frac{EA}{l} - \frac{12EI}{l^3} \right) & \frac{EA}{l} \sin^2 \xi + \frac{12EI}{l^3} \cos^2 \xi & -\frac{6EI}{l^2} \cos \xi \\ \frac{6EI}{l^2} \sin \xi & -\frac{6EI}{l^2} \cos \xi & \frac{4EI}{l} \end{bmatrix} \begin{bmatrix} \delta_{xt} \\ \delta_{yt} \\ \theta_t \end{bmatrix}$$

Then we consider the simplified model as shown on the right side of **Fig. 3a** and redraw the schematic in **Fig. S9c**. We assume it is a planar rigid-joint frame. Beam AC is tilted by an angel β with x direction and beam AD titled by an angel $\gamma = \arctan(\sqrt{2})$. Due to symmetry, node B and C only deform along x direction, node A only deforms along DA direction, and node D is fixed. It is also noted that the cross section area of beam AD is only 1/3 of the original beam AD in the 3D unit cell, and cross section area of beam BC is also only 1/4 of the original beam BC in the 3D unit cell. In the following analysis, we denote beam AB, beam BC, beam AC and beam AD as beam 1, 2, 3 and 4, respectively (**Fig. S9c**). Their physical quantities are expressed

as length l_i , cross section area A_i , the area inertia I_i and Young's modulus E_i (i=1,2,3 or 4).

We can express the relationship between the load and response on nodes for each beam and then assemble it into a larger matrix.

AB beam 1. AB beam is tilted with an angle $\xi = \pi/2$. The load-response relationship can be written as

$$\begin{bmatrix} F_{xA} \\ F_{yA} \\ M_A \end{bmatrix} = \begin{bmatrix} \frac{12E_1I_1}{l_1^3} & 0 & -\frac{6E_1I_1}{l_1^2} \\ 0 & \frac{E_1A_1}{l_1} & 0 \\ -\frac{6E_1I_1}{l_1^2} & 0 & \frac{4E_1I_1}{l_1} \end{bmatrix} \begin{bmatrix} \delta_{xA} \\ \delta_{yA} \\ \theta_A \end{bmatrix} + \begin{bmatrix} -\frac{12E_1I_1}{l_1^3} & 0 & -\frac{6E_1I_1}{l_1^2} \\ 0 & -\frac{E_1A_1}{l_1} & 0 \\ \frac{6E_1I_1}{l_1^2} & 0 & \frac{2E_1I_1}{l_1} \end{bmatrix} \begin{bmatrix} \delta_{xB} \\ 0 \\ \theta_B \end{bmatrix} \quad (S6)$$

$$\begin{bmatrix} F_{xB} \\ F_{yB} \\ M_B \end{bmatrix} = \begin{bmatrix} -\frac{12E_1I_1}{l_1^3} & 0 & \frac{6E_1I_1}{l_1^2} \\ 0 & -\frac{E_1A_1}{l_1} & 0 \\ -\frac{6E_1I_1}{l_1^2} & 0 & \frac{2E_1I_1}{l_1} \end{bmatrix} \begin{bmatrix} \delta_{xA} \\ \delta_{yA} \\ \theta_A \end{bmatrix} + \begin{bmatrix} \frac{12E_1I_1}{l_1^3} & 0 & \frac{6E_1I_1}{l_1^2} \\ 0 & \frac{E_1A_1}{l_1} & 0 \\ \frac{6E_1I_1}{l_1^2} & 0 & \frac{4E_1I_1}{l_1} \end{bmatrix} \begin{bmatrix} \delta_{xB} \\ 0 \\ \theta_B \end{bmatrix} \quad (S7)$$

BC beam 2. AB beam is tilted with an angle $\xi = 0$.

$$\begin{bmatrix} F_{xB} \\ M_B \end{bmatrix} = \begin{bmatrix} \frac{E_2A_2}{l_2} & 0 \\ 0 & \frac{4E_2I_2}{l_2} \end{bmatrix} \begin{bmatrix} \delta_{xB} \\ \theta_B \end{bmatrix} + \begin{bmatrix} -\frac{E_2A_2}{l_2} & 0 \\ 0 & \frac{2E_2I_2}{l_2} \end{bmatrix} \begin{bmatrix} \delta_{xC} \\ \theta_C \end{bmatrix} \quad (S8)$$

$$\begin{bmatrix} F_{xC} \\ M_C \end{bmatrix} = \begin{bmatrix} -\frac{E_2A_2}{l_2} & 0 \\ 0 & \frac{2E_2I_2}{l_2} \end{bmatrix} \begin{bmatrix} \delta_{xB} \\ \theta_B \end{bmatrix} + \begin{bmatrix} \frac{E_2A_2}{l_2} & 0 \\ 0 & \frac{4E_2I_2}{l_2} \end{bmatrix} \begin{bmatrix} \delta_{xC} \\ \theta_C \end{bmatrix} \quad (S9)$$

AC beam 3. AC beam is titled with an angle $\xi = \beta$.

$$\begin{bmatrix} F_{xA} \\ F_{yA} \\ M_A \end{bmatrix} = \begin{bmatrix} \frac{E_3 A_3}{l_3} \cos^2 \beta + \frac{12 E_3 I_3}{l_3^3} \sin^2 \beta & \sin \beta \cos \beta \left(\frac{E_3 A_3}{l_3} - \frac{12 E_3 I_3}{l_3^3} \right) & -\frac{6 E_3 I_3}{l_3^2} \sin \beta \\ \sin \beta \cos \beta \left(\frac{E_3 A_3}{l_3} - \frac{12 E_3 I_3}{l_3^3} \right) & \frac{E_3 A_3}{l_3} \sin^2 \beta + \frac{12 E_3 I_3}{l_3^3} \cos^2 \beta & \frac{6 E_3 I_3}{l_3^2} \cos \beta \\ -\frac{6 E_3 I_3}{l_3^2} \sin \beta & \frac{6 E_3 I_3}{l_3^2} \cos \beta & \frac{4 E_3 I_3}{l_3} \end{bmatrix} \begin{bmatrix} \delta_{xA} \\ \delta_{yA} \\ \theta_A \end{bmatrix} \quad (\text{S10})$$

$$+ \begin{bmatrix} -\frac{E_3 A_3}{l_3} \cos^2 \beta - \frac{12 E_3 I_3}{l_3^3} \sin^2 \beta & \sin \beta \cos \beta \left(-\frac{E_3 A_3}{l_3} + \frac{12 E_3 I_3}{l_3^3} \right) & -\frac{6 E_3 I_3}{l_3^2} \sin \beta \\ \sin \beta \cos \beta \left(-\frac{E_3 A_3}{l_3} + \frac{12 E_3 I_3}{l_3^3} \right) & -\frac{E_3 A_3}{l_3} \sin^2 \beta - \frac{12 E_3 I_3}{l_3^3} \cos^2 \beta & \frac{6 E_3 I_3}{l_3^2} \cos \beta \\ \frac{6 E_3 I_3}{l_3^2} \sin \beta & -\frac{6 E_3 I_3}{l_3^2} \cos \beta & \frac{2 E_3 I_3}{l_3} \end{bmatrix} \begin{bmatrix} \delta_{xC} \\ 0 \\ \theta_C \end{bmatrix}$$

$$\begin{bmatrix} F_{xC} \\ F_{yC} \\ M_C \end{bmatrix} = \begin{bmatrix} -\frac{E_3 A_3}{l_3} \cos^2 \beta - \frac{12 E_3 I_3}{l_3^3} \sin^2 \beta & \sin \beta \cos \beta \left(-\frac{E_3 A_3}{l_3} + \frac{12 E_3 I_3}{l_3^3} \right) & \frac{6 E_3 I_3}{l_3^2} \sin \beta \\ \sin \beta \cos \beta \left(-\frac{E_3 A_3}{l_3} + \frac{12 E_3 I_3}{l_3^3} \right) & -\frac{E_3 A_3}{l_3} \sin^2 \beta - \frac{12 E_3 I_3}{l_3^3} \cos^2 \beta & -\frac{6 E_3 I_3}{l_3^2} \cos \beta \\ -\frac{6 E_3 I_3}{l_3^2} \sin \beta & \frac{6 E_3 I_3}{l_3^2} \cos \beta & \frac{2 E_3 I_3}{l_3} \end{bmatrix} \begin{bmatrix} \delta_{xA} \\ \delta_{yA} \\ \theta_A \end{bmatrix} \quad (\text{S11})$$

$$+ \begin{bmatrix} \frac{E_3 A_3}{l_3} \cos^2 \beta + \frac{12 E_3 I_3}{l_3^3} \sin^2 \beta & \sin \beta \cos \beta \left(\frac{E_3 A_3}{l_3} - \frac{12 E_3 I_3}{l_3^3} \right) & \frac{6 E_3 I_3}{l_3^2} \sin \beta \\ \sin \beta \cos \beta \left(\frac{E_3 A_3}{l_3} - \frac{12 E_3 I_3}{l_3^3} \right) & \frac{E_3 A_3}{l_3} \sin^2 \beta + \frac{12 E_3 I_3}{l_3^3} \cos^2 \beta & -\frac{6 E_3 I_3}{l_3^2} \cos \beta \\ \frac{6 E_3 I_3}{l_3^2} \sin \beta & -\frac{6 E_3 I_3}{l_3^2} \cos \beta & \frac{4 E_3 I_3}{l_3} \end{bmatrix} \begin{bmatrix} \delta_{xC} \\ 0 \\ \theta_C \end{bmatrix}$$

AD beam 4. AD beam is titled with an angle $\xi = \gamma = \arctan(\sqrt{2})$.

$$\begin{bmatrix} F_{xA} \\ F_{yA} \\ M_A \end{bmatrix} = \begin{bmatrix} \frac{E_4 A_4}{l_4} \cos^2 \gamma + \frac{12 E_4 I_4}{l_4^3} \sin^2 \gamma & \sin \gamma \cos \gamma \left(\frac{E_4 A_4}{l_4} - \frac{12 E_4 I_4}{l_4^3} \right) & -\frac{6 E_4 I_4}{l_4^2} \sin \gamma \\ \sin \gamma \cos \gamma \left(\frac{E_4 A_4}{l_4} - \frac{12 E_4 I_4}{l_4^3} \right) & \frac{E_4 A_4}{l_4} \sin^2 \gamma + \frac{12 E_4 I_4}{l_4^3} \cos^2 \gamma & \frac{6 E_4 I_4}{l_4^2} \cos \gamma \\ -\frac{6 E_4 I_4}{l_4^2} \sin \gamma & \frac{6 E_4 I_4}{l_4^2} \cos \gamma & \frac{4 E_4 I_4}{l_4} \end{bmatrix} \begin{bmatrix} \delta_{xA} \\ \delta_{yA} \\ \theta_A \end{bmatrix} \quad (\text{S12})$$

We assemble **Eqs. S6-S12** into one equation as

$$\begin{bmatrix} c_{11} & \dots \\ \dots & \dots \\ c_{71} \end{bmatrix} c_{17} \begin{bmatrix} \delta_{xA} \\ \delta_{yA} \\ \theta_A \\ \delta_{xB} \\ \theta_B \\ \delta_{xC} \\ \theta_C \end{bmatrix} = \begin{bmatrix} F_{xA} \\ F_{yA} \\ M_A \\ F_{xB} \\ M_B \\ F_{xC} \\ M_C \end{bmatrix} \quad (S13)$$

where the nonzero terms of the left side structural matrix c_{ij} ($1 \leq i \leq 7, 1 \leq j \leq 7$) include the following:

$$\begin{aligned}
c_{11} &= \frac{12E_1I_1}{l_1^3} + \frac{E_3A_3}{l_3} \cos^2 \beta + \frac{12E_3I_3}{l_3^3} \sin^2 \beta + \frac{E_4A_4}{l_4} \cos^2 \gamma + \frac{12E_4I_4}{l_4^3} \sin^2 \gamma \\
c_{12} &= \sin \beta \cos \beta \left(\frac{E_3A_3}{l_3} - \frac{12E_3I_3}{l_3^3} \right) + \sin \gamma \cos \gamma \left(\frac{E_4A_4}{l_4} - \frac{12E_4I_4}{l_4^3} \right) \\
c_{13} &= -\frac{6E_1I_1}{l_1^2} - \frac{6E_3I_3}{l_3^2} \sin \beta - \frac{6E_4I_4}{l_4^2} \sin \gamma \\
c_{14} &= -\frac{12E_1I_1}{l_1^3} \\
c_{15} &= -\frac{6E_1I_1}{l_1^2} \\
c_{16} &= -\frac{E_3A_3}{l_3} \cos^2 \beta - \frac{12E_3I_3}{l_3^3} \sin^2 \beta \\
c_{17} &= -\frac{6E_3I_3}{l_3^2} \sin \beta \\
c_{21} &= \sin \beta \cos \beta \left(\frac{E_3A_3}{l_3} - \frac{12E_3I_3}{l_3^3} \right) + \sin \gamma \cos \gamma \left(\frac{E_4A_4}{l_4} - \frac{12E_4I_4}{l_4^3} \right) \\
c_{22} &= \frac{E_1A_1}{l_1} + \frac{E_3A_3}{l_3} \sin^2 \beta + \frac{12E_3I_3}{l_3^3} \cos^2 \beta + \frac{E_4A_4}{l_4} \sin^2 \gamma + \frac{12E_4I_4}{l_4^3} \cos^2 \gamma \\
c_{23} &= \frac{6E_3I_3}{l_3^2} \cos \beta + \frac{6E_4I_4}{l_4^2} \cos \gamma \\
c_{26} &= \sin \beta \cos \beta \left(-\frac{E_3A_3}{l_3} + \frac{12E_3I_3}{l_3^3} \right) \\
c_{27} &= \frac{6E_3I_3}{l_3^2} \cos \beta
\end{aligned}$$

$$c_{31} = -\frac{6E_1I_1}{l_1^2} - \frac{6E_3I_3}{l_3^2} \sin \beta - \frac{6E_4I_4}{l_4^2} \sin \gamma$$

$$c_{32} = \frac{6E_3I_3}{l_3^2} \cos \beta + \frac{6E_4I_4}{l_4^2} \cos \gamma$$

$$c_{33} = \frac{4E_1I_1}{l_1} + \frac{4E_3I_3}{l_3} + \frac{4E_4I_4}{l_4}$$

$$c_{34} = \frac{6E_1I_1}{l_1^2}$$

$$c_{35} = \frac{2E_1I_1}{l_1}$$

$$c_{36} = \frac{6E_3I_3}{l_3^2} \sin \beta$$

$$c_{37} = \frac{2E_3I_3}{l_3}$$

$$c_{41} = -\frac{12E_1I_1}{l_1^3}$$

$$c_{43} = \frac{6E_1I_1}{l_1^2}$$

$$c_{44} = \frac{12E_1I_1}{l_1^3} + \frac{E_2A_2}{l_2}$$

$$c_{45} = \frac{6E_1I_1}{l_1^2}$$

$$c_{46} = -\frac{E_2A_2}{l_2}$$

$$c_{51} = -\frac{6E_1I_1}{l_1^2}$$

$$c_{53} = \frac{2E_1I_1}{l_1}$$

$$c_{54} = \frac{6E_1I_1}{l_1^2}$$

$$c_{55} = \frac{4E_1I_1}{l_1} + \frac{4E_2I_2}{l_2}$$

$$c_{57} = \frac{2E_2I_2}{l_2}$$

$$\begin{aligned}
c_{61} &= -\frac{E_3 A_3}{l_3} \cos^2 \beta - \frac{12 E_3 I_3}{l_3^3} \sin^2 \beta \\
c_{62} &= \sin \beta \cos \beta \left(-\frac{E_3 A_3}{l_3} + \frac{12 E_3 I_3}{l_3^3} \right) \\
c_{63} &= \frac{6 E_3 I_3}{l_3^2} \sin \beta \\
c_{64} &= -\frac{E_2 A_2}{l_2} \\
c_{66} &= \frac{E_2 A_2}{l_2} + \frac{E_3 A_3}{l_3} \cos^2 \beta + \frac{12 E_3 I_3}{l_3^3} \sin^2 \beta \\
c_{67} &= \frac{4 E_3 I_3}{l_3} + \frac{6 E_3 I_3}{l_3^2} \sin \beta \\
c_{71} &= -\frac{6 E_3 I_3}{l_3^2} \sin \beta \\
c_{72} &= \frac{6 E_3 I_3}{l_3^2} \cos \beta \\
c_{73} &= \frac{2 E_3 I_3}{l_3} \\
c_{75} &= \frac{2 E_2 I_2}{l_2} \\
c_{76} &= \frac{6 E_3 I_3}{l_3^2} \sin \beta \\
c_{77} &= \frac{4 E_3 I_3}{l_3} + \frac{4 E_2 I_2}{l_2}
\end{aligned}$$

Here, we consider the thermal load applied on the beams. The loading vector can be expressed as

$$\begin{bmatrix} F_{xA} \\ F_{yA} \\ M_A \\ F_{xB} \\ M_B \\ F_{xC} \\ M_C \end{bmatrix} = \begin{bmatrix} -E_3 A_3 \alpha_1 \Delta T \cos \beta - E_4 A_4 \alpha_2 \Delta T \cos \gamma \\ -E_1 A_1 \alpha_2 \Delta T - E_3 A_3 \alpha_1 \Delta T \sin \beta - E_4 A_4 \alpha_2 \Delta T \sin \gamma \\ 0 \\ -E_2 A_2 \alpha_2 \Delta T \\ 0 \\ E_2 A_2 \alpha_2 \Delta T + E_3 A_3 \alpha_1 \Delta T \cos \beta \\ 0 \end{bmatrix} \quad (\text{S14})$$

where α_1 and α_2 are the thermal expansion coefficient of the PEGDA beam and reinforced beam, respectively.

Combining **Eqs. S13** and **S14**, we can calculate δ_{xB} . By further including the thermal expansion of beam BE in **Fig. S9c**, we can calculate the effective expansion ratio as


$$\eta = -\frac{2(\delta_{xB} - \alpha_1 \Delta T l_{BE})}{\sqrt{2}l_{AB} + 2L_{BE}} \quad (\text{S15})$$

The above analytical model (especially **Eqs. S13-S15**) can perfectly echo with the prediction given by **Eq. 2**, i.e., the effective expansion ratio increases with decreasing thermal expansion coefficients α_2/α_1 of two types of beams, and increases with increasing angel β ($\arctan(\sqrt{2}) < \beta < \pi/2$). However, the analytical model considers the jointing of beams is ideal rigid jointing, and the beam jointing within the fabricated sample may have complex overlaps. The analytical model is not able to quantitatively predict the experimentally observed values of negative thermal expansions. As a result, we turn to finite element calculations that can match quantitatively with our experimental results as shown in **Fig. 3bc**.

1.4. Finite element analysis of the lattice structure

The finite element analyses of the lattice structure are shown in **Fig. S8**. All 1/8 models of the unit cells are first designed in Solidworks and imported into a commercial code ABAQUS 6.10.1 to implement the finite element analyses. The two types of beams are taken to obey thermoelastic model with mechanical parameters shown in **Table S1**. The models are discretized by C3D8H elements with more than 40,000 elements. Thermomechanical analyses are performed with increasing temperature. The result accuracy is ascertained through mesh refinement studies. The computation for each case takes around 1 hour. 2D view and 3D view of the finite element analyses are shown in Supplemental Movie S2 and S3, respectively.

2. Supplemental Figures

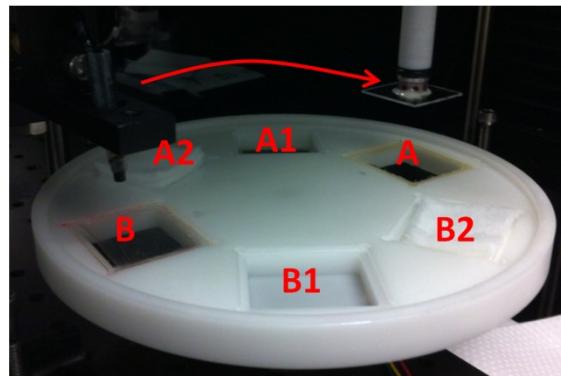

- A: window for material A
- A1: ethanol for material A
- A2: cotton for material A
- B: window for material B
- B1: ethanol for material B
- B2: cotton for material B

FIG. S1. The design of the rotating wheel for delivering polymer solutions.

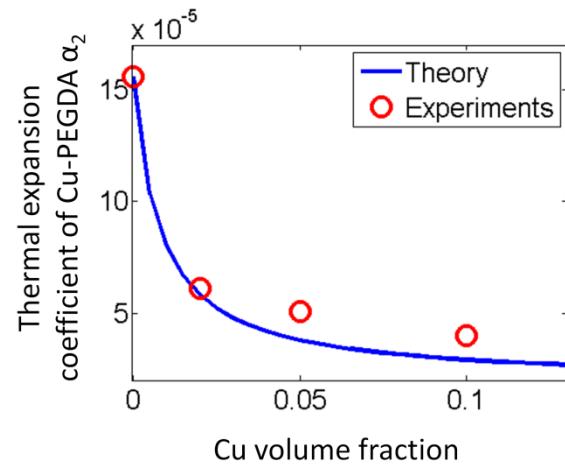


FIG. S2. Theoretically predicted and experimentally measured thermal expansion coefficients of Cu-PEGDA nanocomposite in functions of Cu volume fractions.

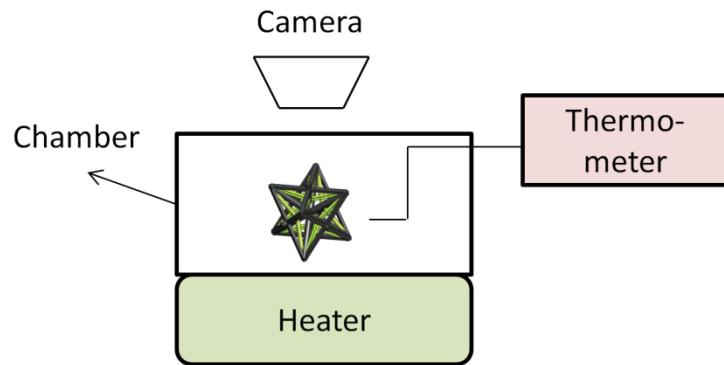


FIG. S3. Schematic of setup for the heating experiment.

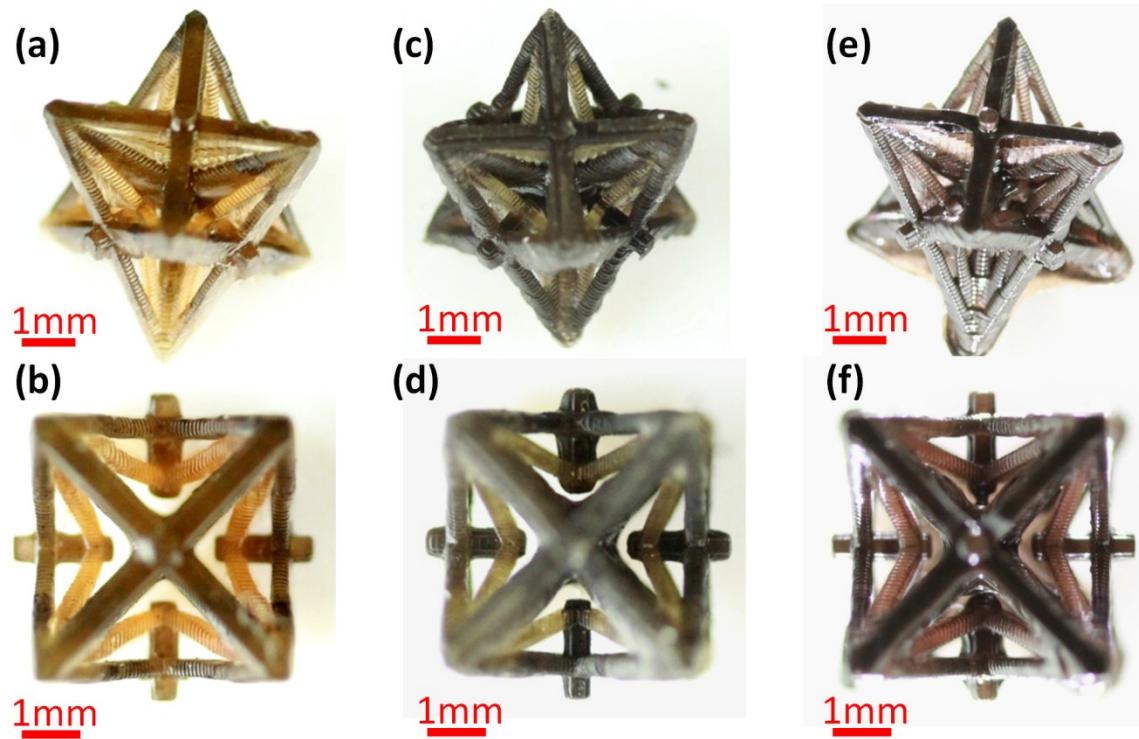


FIG. S4. 3D view (a, c, and e) and 2D view (b, d, and f) of fabricated unit cells consisted of PEGDA beams and reinforced beams with 2% vol copper (ab), 5% vol copper (cd) and 10% copper (ef).

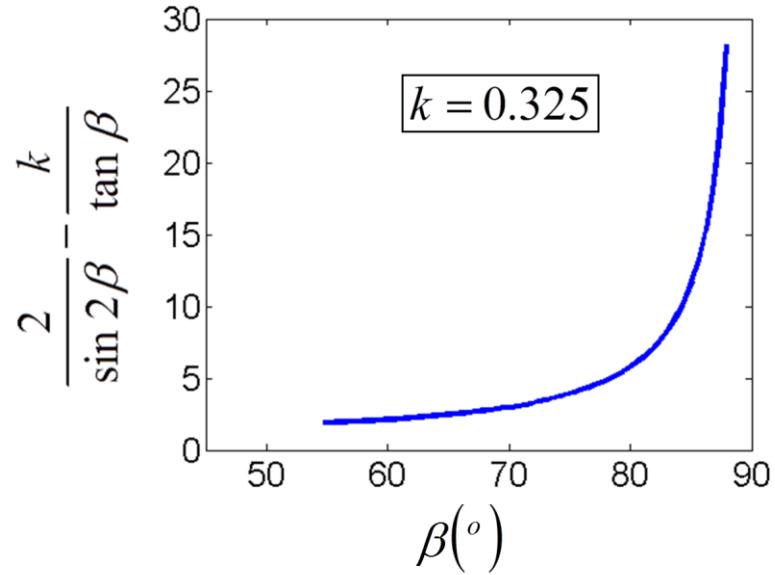


FIG. S5. The function $\frac{2}{\sin 2\beta} - \frac{k}{\tan \beta}$ plotted with increasing angle β . The thermal expansion coefficient ratio k is set as the ratio between thermal expansion coefficient of the reinforced beam with 5%vol copper ($4.0 \times 10^{-5} \text{ K}^{-1}$) and that of PEGDA beam ($1.56 \times 10^{-4} \text{ K}^{-1}$).

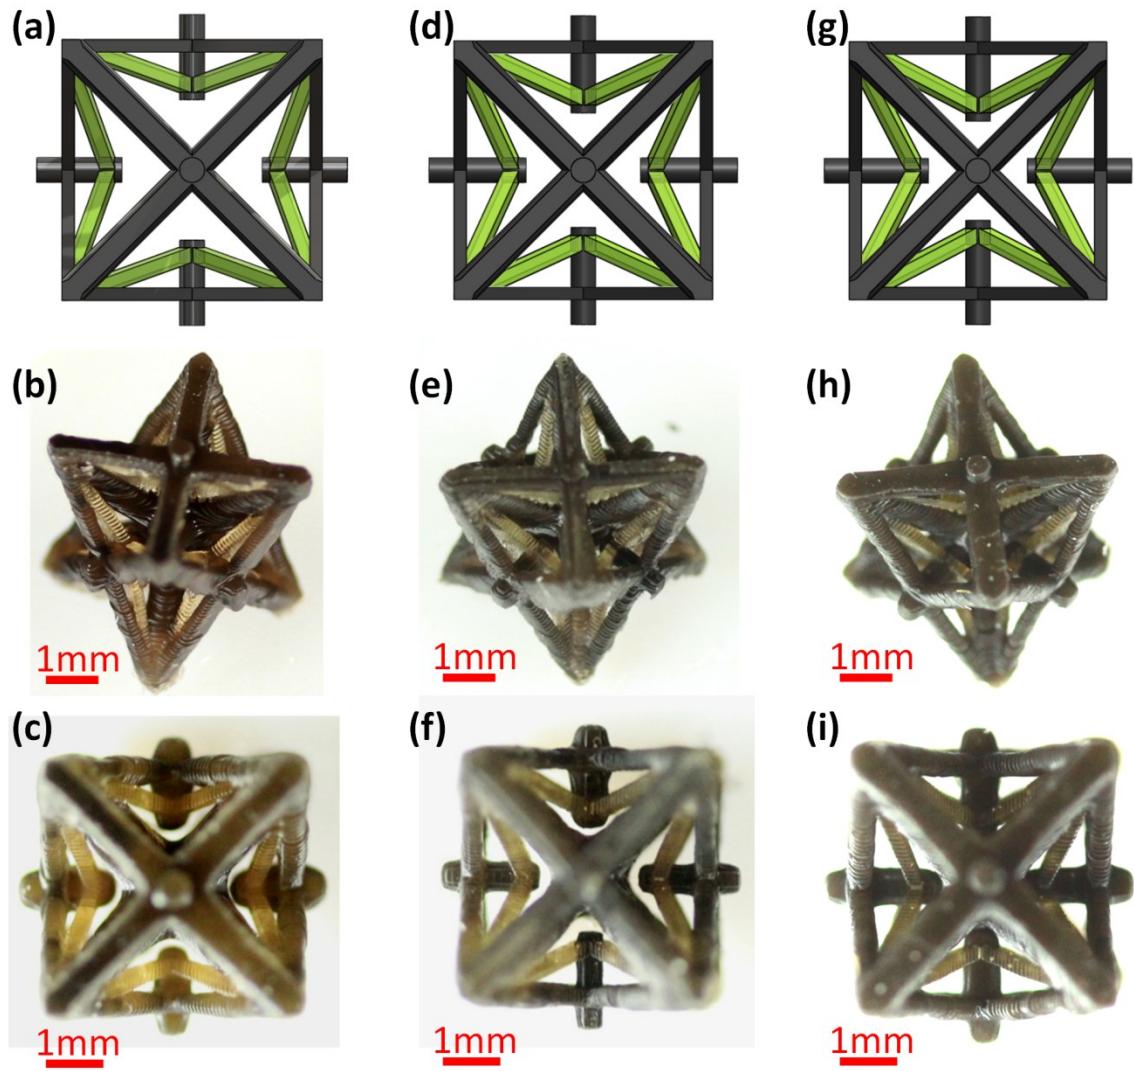


FIG. S6. CAD design (a, d, and g), 3D views (b, e, and h) and 2D views (c, f, and i) of the fabricated unit cells with varied BC beam length, 0.74mm (a-c), 0.97mm(d-f) and 1.17mm(g-i), respectively.

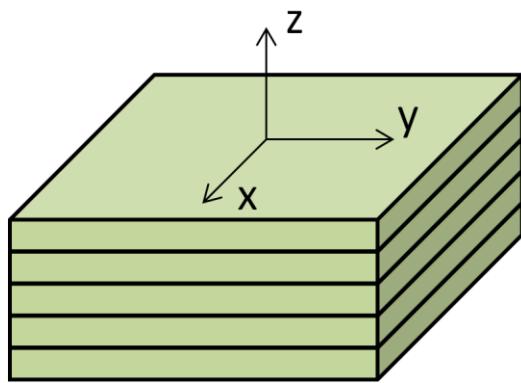


FIG. S7. A schematic to show a fabricated sample with printed layers. The mechanical properties along x (or y) direction may be different from those along z direction.

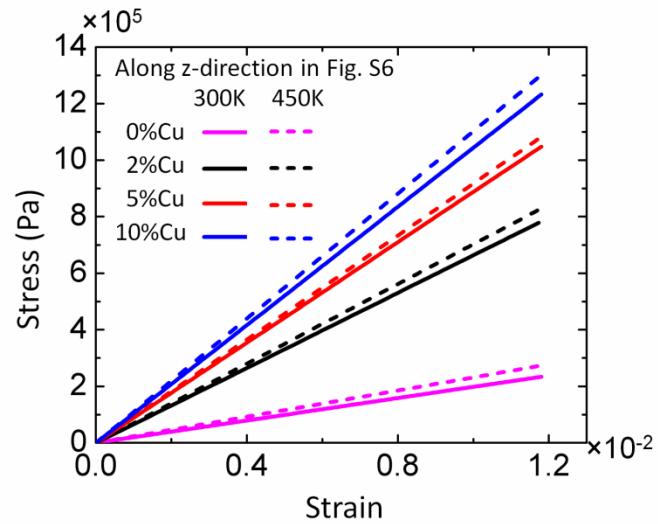


FIG S8. Measured compressive stress-strain behaviors of the reinforced and unreinforced beams with varied copper volume fractions at 300K and 450K. The Young's moduli of all beams change slightly from 300K to 450K. All data are measured along z-direction shown in Fig. S6.

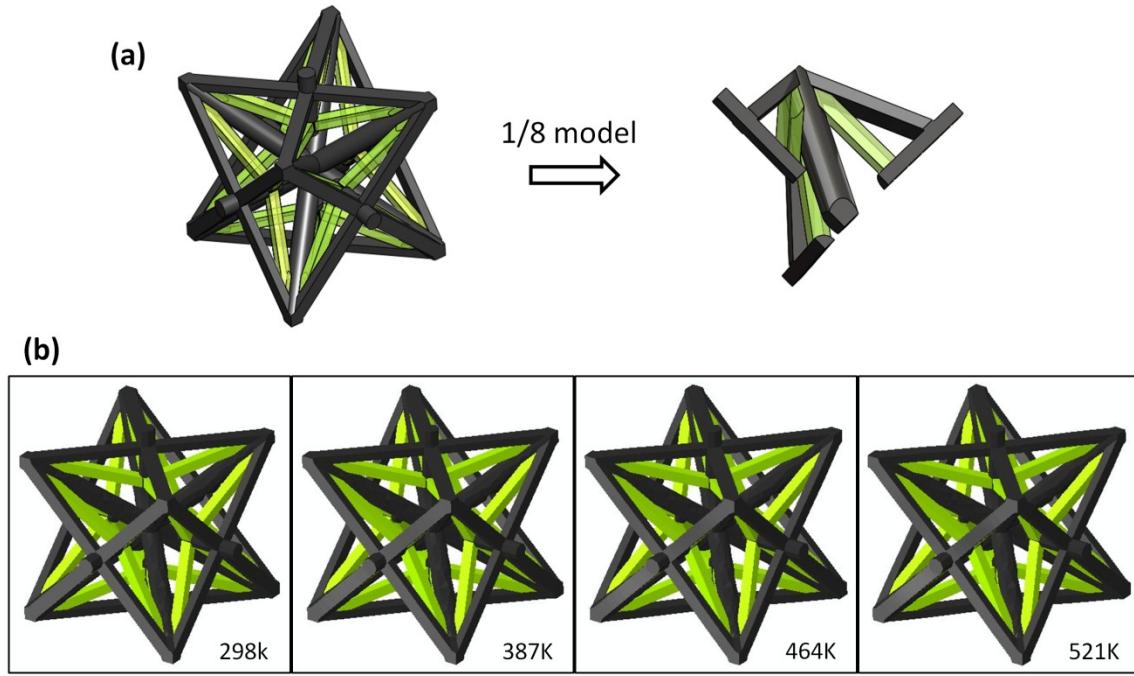


FIG S9. (a) 1/8 model of the unit cell is used for the finite element calculation. (b) Finite element simulation sequence of the 3D unit cell with increasing temperature (more details in **Supplemental Movie S4**).

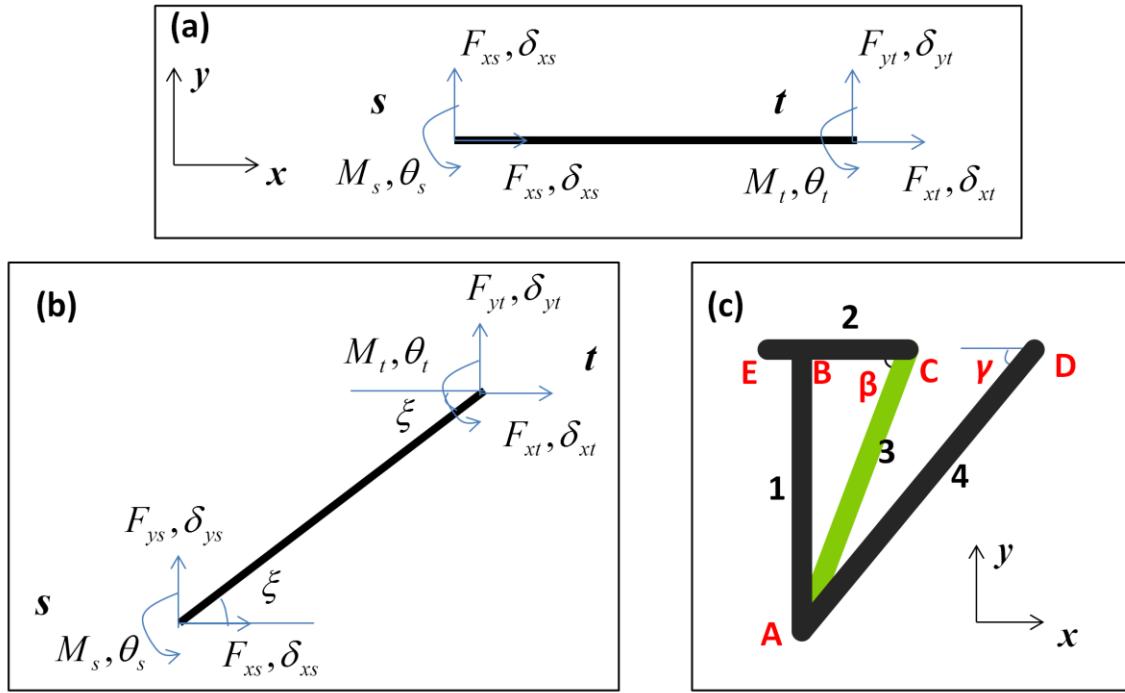


FIG S10. Schematics to show the stress states of (a) a horizontal beam and (b) a tilted beam. (c) A simplified model of the unit cell as shown in **Fig. 3a**.

3. Supplemental Table

TABLE S1. Thermomechanical properties of PEDGA beams and reinforced PEGDA beams.

Properties	Materials	PEGDA	2Vol% Cu-PEGDA	5Vol% Cu-PEGDA	10Vol% Cu-PEGDA
Young's modulus $E_x = E_y$ (Mpa)	20.3	67.2	90.7	105.5	
Young's modulus E_z (MPa)	23.5	71.1	92.2	112.4	
Effective Young's modulus E (MPa)	21.9	69.2	91.5	108.9	
Poisson's ratio	~0.4	~0.3	~0.3	~0.3	
Thermal expansion coefficient $\alpha_x = \alpha_y$ ($\times 10^{-6} \text{ K}^{-1}$)	153	62.6	51.2	41.4	
Thermal expansion coefficient α_z ($\times 10^{-6} \text{ K}^{-1}$)	158.2	59.2	49	38.2	
Effective thermal expansion coefficient α ($\times 10^{-6} \text{ K}^{-1}$)	155.6	60.9	50.6	39.8	

4. Supplemental Movie

Supplemental Movie S1. Geometrical evolution of the fabricated unit cell with increasing temperature.

Supplemental Movie S2. 3D view of geometrical evolution of the FEA simulated unit cell with increasing temperature.

Supplemental Movie S3. 2D view of geometrical evolution of the FEA simulated unit cell with increasing temperature.

Supplemental Movie S4. Geometrical evolution of the fabricated 2 by 2 composite lattice with increasing temperature.

Reference

- [1] K. Arcaute, B. Mann, and R. Wicker, *Acta Biomater.* **6**, 1047 (2010).
- [2] J.-W. Choi, H.-C. Kim, and R. Wicker, *J. Mater. Process. Technol.* **211**, 318 (2011).
- [3] C. Zhou, Y. Chen, Z. Yang, and B. Khoshnevis, in *Annual Solid Freeform Fabrication Symposium, Austin, TX2011*.
- [4] X. Zheng, J. Deotte, M. P. Alonso, G. R. Farquar, T. H. Weisgraber, S. Gemberling, H. Lee, N. Fang, and C. M. Spadaccini, *Rev. Sci. Instrum.* **83**, 125001 (2012).
- [5] X. Zheng *et al.*, *Science* **344**, 1373 (2014).
- [6] H. Lee, J. Zhang, H. Jiang, and N. X. Fang, *Phys. Rev. Lett.* **108**, 214304 (2012).
- [7] J. Bauer, S. Hengsbach, I. Tesari, R. Schwaiger, and O. Kraft, *Proc. Nat. Acad. Sci. U.S.A.* **111**, 2453 (2014).
- [8] L. R. Meza, S. Das, and J. R. Greer, *Science* **345**, 1322 (2014).
- [9] J. R. Tumbleston *et al.*, *Science* **347**, 1349 (2015).
- [10] T. A. Schaedler, A. J. Jacobsen, A. Torrents, A. E. Sorensen, J. Lian, J. R. Greer, L. Valdevit, and W. B. Carter, *Science* **334**, 962 (2011).
- [11] R. M. Jones, *Mechanics of composite materials* (Scripta Book Company Washington, DC, 1975), Vol. 193.
- [12] J. D. Renton, *Elastic Beams and Frames* (Elsevier, 2002).