

Miniemulsion ARGET ATRP via Interfacial and Ion-Pair Catalysis: From ppm to ppb of Residual Copper

Yi Wang,[†] Francesca Lorandi,^{‡,§} Marco Fantin,[†] Paweł Chmielarz,^{†,§} Abdirisak A. Isse,[‡] Armando Gennaro,[‡] and Krzysztof Matyjaszewski^{*,†}


[†]Department of Chemistry, Carnegie Mellon University, 4400 Fifth Avenue, Pittsburgh, Pennsylvania 15213, United States

[‡]Department of Chemical Sciences, University of Padova, Via Marzolo 1, 35131 Padova, Italy

[§]Department of Physical Chemistry, Faculty of Chemistry, Rzeszów University of Technology, Al. Powstańców Warszawy 6, 35-959 Rzeszów, Poland

Supporting Information

ABSTRACT: It was recently reported that copper catalysts used in atom transfer radical polymerization (ATRP) can combine with anionic surfactants used in emulsion polymerization to form ion pairs. The ion pairs predominately reside at the surface of the monomer droplets, but they can also migrate inside the droplets and induce a controlled polymerization. This concept was applied to activator regenerated by electron transfer (ARGET) ATRP, with ascorbic acid as reducing agent. ATRP of *n*-butyl acrylate (BA) and *n*-butyl methacrylate (BMA) was carried out in miniemulsion using Cu^{II}/tris(2-pyridylmethyl)amine (TPMA) as catalyst, with several anionic surfactants forming the reactive ion-pair complexes. The amount and structure of surfactant controlled both the polymerization rate and the final particle size. Well-controlled polymers were prepared with catalyst loadings as low as 50 ppm, leaving only 300 ppb of Cu in the precipitated polymer. Efficient chain extension of a poly(BMA)-Br macroinitiator confirmed high retention of chain-end functionality. This procedure was exploited to prepare polymers with complex architectures such as block copolymers, star polymers, and molecular brushes.

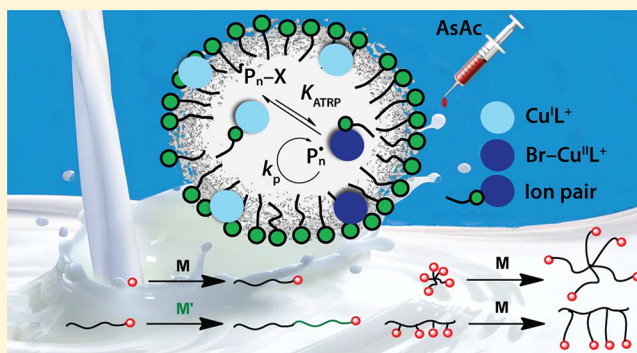

1. INTRODUCTION


Reversible-deactivation radical polymerizations (RDRPs) in heterogeneous media are characterized by good heat transfer, low environmental impact, low viscosity, and low toxicity,¹ which are important advantages for commercial applications.² Moreover, polymerization in dispersed media, including microemulsion, miniemulsion, emulsion, and dispersion, can be used to prepare nanoparticles with various morphologies (e.g. core-shell, microcapsules and multilayered particles) for specific applications in biomedical, pharmaceutical, drug delivery, or diagnostic areas.^{1,3–6}

RDRPs provide well-defined polymers with low dispersity ($\bar{D}$), limited amount of radical termination, and predetermined architecture and molecular weight (MW).^{7–9} The most often used RDRP methods are atom transfer radical polymerization (ATRP), reversible addition-fragmentation chain-transfer (RAFT) polymerization, and nitroxide-mediated polymerization (NMP), which have been successfully developed in both homogeneous and heterogeneous media.^{9–15} Moreover, heterogeneous systems additionally limit radical termination through radical segregation and compartmentalization.^{16–18} Despite the benefits offered by dispersed media, the vast

majority of RDRPs are still performed in homogeneous systems.

A promising technique for heterogeneous polymerization is ATRP, which is based on radical generation by an active catalyst, generally a copper-amine complex in its lower oxidation state, i.e., Cu^IL⁺ (Scheme 1).¹⁹ The Cu^IL⁺ complex activates an alkyl halide initiator (R-X) or dormant chain end (P_n-X), forming a propagating radical and a higher oxidation state deactivator complex X-Cu^{II}L⁺. A small fraction of chains is active at one time and initiation can be fast; therefore, all chains grow homogeneously and termination reactions are minimized.²⁰

Scheme 1. Mechanism of ATRP

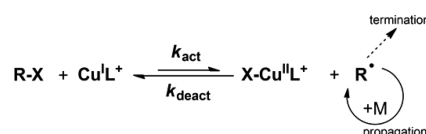


Received: August 9, 2017

Revised: September 28, 2017

Published: November 3, 2017

Scheme 2. Mechanism of Ion-Pair and Interfacial Catalysis in ARGET ATRP in Miniemulsion with Ascorbic Acid as Reducing Agent

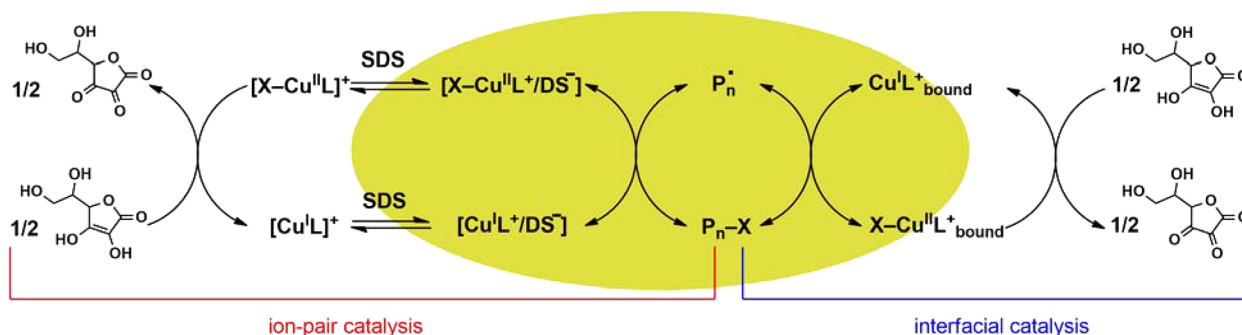

During the past decade, catalyst loading was reduced by the development of “low-ppm” ATRP techniques. These methods comprise activators regenerated by electron transfer (ARGET) ATRP,^{21,22} initiators for continuous activator regeneration (ICAR) ATRP,²³ supplemental activator and reducing agent (SARA) ATRP,^{24–28} electrochemically mediated ATRP (eATRP),^{29–33} photoATRP,^{34,35} and mechanoATRP.^{36,37} Nevertheless, for some applications, residual catalyst should be removed, using column filtration, electrodeposition, or more complex methods, depending on the desired degree of purity.^{38–43}


The biphasic nature of heterogeneous polymerizations can simplify catalyst removal. Indeed, in miniemulsion systems, the large surface area of the organic/water interface helps mass transport of the catalyst from the polymer particles to the aqueous phase, if a sufficiently hydrophilic catalyst is used. The catalyst, however, should be also sufficiently hydrophobic to enter the hydrophobic monomer droplets, where it starts and controls the miniemulsion polymerization.^{1,44}

In this context, we recently developed a novel catalytic system for eATRP, based on a strongly hydrophilic complex, Br–Cu^{II}TPMA⁺. Despite its insoluble nature in *n*-butyl acrylate (BA), the catalyst enters hydrophobic BA droplets when combined with an anionic surfactant, sodium dodecyl sulfate (SDS).⁴⁵ The interaction between catalyst and SDS formed neutral ion pairs, Br–Cu^{II}TPMA⁺/DS[–], that resided either at the surface or inside the BA droplets. This concept could be considered as a paradigm shift for miniemulsion ATRP, which previously required very hydrophobic catalysts that were predominately confined to the organic phase.^{46–50} With the Br–Cu^{II}TPMA⁺/SDS system, only ~1% of the catalyst was inside the hydrophobic droplets as ion pairs, 95% was bound at the monomer/water interface, and ~4% was in the aqueous phase. Therefore, such a combination of ion-pair and interfacial catalysis (cf. Scheme 2) allowed for the successful eATRP of BA. Relevant for industrial application, ≤1% of total Cu was detected inside the final latex after centrifugation.


In the present work, the concept of ion-pair and interfacial catalysis was exploited in miniemulsion ARGET ATRP of BA and *n*-butyl methacrylate (BMA), with ascorbic acid (AsAc) as reducing agent (Scheme 2). Several hydrophilic ligands and anionic surfactants were evaluated (Scheme 3). The effect of SDS concentration on particles size, polymerization kinetics, and degree of control was studied, providing some mechanistic insights. Cu concentration was reduced to minimize contamination in the final product. Both low and high degrees of polymerization (200–1200) were targeted. The livingness of the process was confirmed by chain-extending a poly(*n*-butyl

Scheme 3. Chemical Structures of Copper Ligands, Surfactants, and Initiators Used in This Work


• LIGANDS

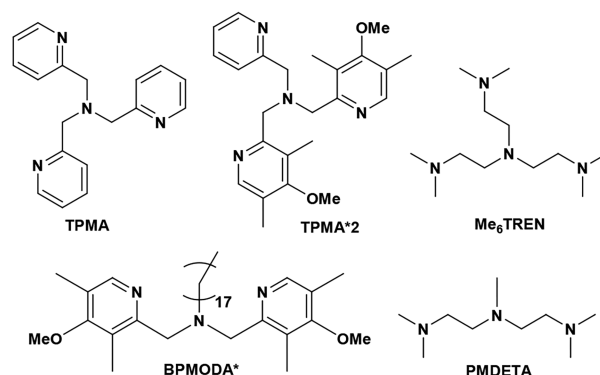

• SURFACTANTS



• INITIATORS

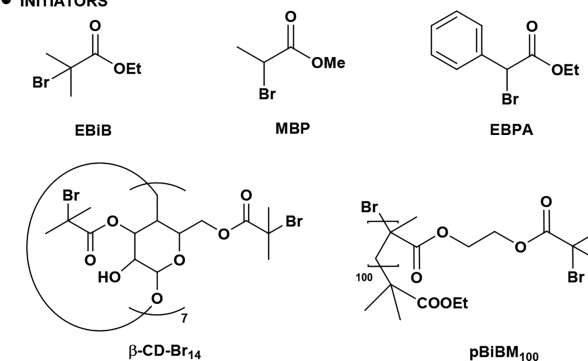

methacrylate)–Br macroinitiator (PBMA-MI) with both acrylic and methacrylic monomers, confirming the high retention of chain-end functionality. Synthesis of polymers with complex architecture, such as stars and brushes, was successful.⁵¹

2. RESULTS AND DISCUSSION

Effect of Ligand Structure on Miniemulsion ATRP of BA. Different copper complexes were tested in ARGET ATRP with 20 vol % BA in water, using ultrasonication to form a miniemulsion with the composition reported in Table 1. NaBr

Table 1. Composition of Organic and Aqueous Phases in a Typical Miniemulsion ARGET ATRP^a

component	weight (g)	comments
<i>organic phase</i>		
monomer	1.79	20 vol % (18 wt %)
R-X ^{b,c}	0.0098 (EBiB), 0.0109 (EBPA)	[monomer]/[R-X] = 280/1
hexadecane	0.19	10.8 wt % to monomer
<i>aqueous phase</i>		
water	8	deionized water
SDS ^c	0.082	4.6 wt % to monomer
NaBr	0.103	[NaBr] = 0.1 M ^d
Cu ^{II} Br ₂	2.2 × 10 ⁻³	1 mM ^d
TPMA ^c	2.4 × 10 ⁻³	1.1 mM ^d
AsAc	varied	cf. Tables 2–5

^aConditions: $T = 65\text{ }^{\circ}\text{C}$, $V_{\text{tot}} = 10\text{ mL}$. The miniemulsion was prepared by ultrasonication as described in the [Supporting Information](#). ^b[R-X] was varied to target different degrees of polymerization (DPs). ^cChemical structures of surfactants, initiators, and ligands are presented in [Scheme 3](#). ^dWith respect to the total volume.

(0.1 M) was added to increase the stability of the Br-Cu^{II}L⁺ deactivator, which could otherwise dissociate to Cu^{II}L²⁺ + Br⁻ in aqueous media.^{52,53} The appropriate amount of AsAc was injected dropwise during the first 3 min of the reaction, considering that reduction of all Cu^{II} requires [AsAc]/[Cu^{II}] = 0.5.⁴⁶

The Cu complexes with pyridinic ligands, Br-Cu^{II}TPMA⁺ and Br-Cu^{II}(TPMA*2)⁺, provided well-controlled PBA with $\bar{D} \approx 1.2$ and experimental MW ($M_{n,\text{app}}$) close to theoretical values ([Table 2](#), entries 1–3). The obtained latex was stable for several months, and particle size varied less than 15% before and after polymerizations, as measured by dynamic light scattering (DLS). Comparable results were obtained using either NaBr or Et₄NBr as a source of Br⁻ to stabilize Br-Cu^{II}TPMA⁺ ([Table 2](#), entry 1 vs 2). Et₄NBr, however, formed larger monomer droplets, indicating that Et₄N⁺ can slightly destabilize latex formation.

The polymerization rates were almost the same with Br-Cu^{II}TPMA⁺ and Br-Cu^{II}(TPMA*2)⁺, despite the much higher redox activity of the latter catalyst. On the other hand, the interactions between SDS and either Br-Cu^{II}(TPMA*2)⁺ or Br-Cu^{II}TPMA⁺ were similar.⁴⁵ This indicates that the intrinsic catalyst activity, catalyst interaction with the surfactant, and the partitioning of the catalyst between the organic and aqueous phases are all important parameters.

Me₆TREN and PMDETA were also tested as ligands under otherwise identical conditions. These aliphatic-amine ligands

led to 6–9 times faster polymerizations than with TPMA, but poorly controlled ([Table 2](#), entries 3 and 4). Similar poor control was previously observed in eATRP with Me₆TREN and attributed to a much weaker interaction between SDS and Br-Cu^{II}Me₆TREN⁺ than with Br-Cu^{II}TPMA⁺. Moreover, previous electrochemical studies showed that the interaction between Cu/Me₆TREN and SDS was stronger for Cu^I than Cu^{II} species. Abundant Cu^IMe₆TREN⁺/DS⁻ explains the faster polymerization, while scarce Br-Cu^{II}Me₆TREN⁺/DS⁻ suggests that insufficient deactivator was present at the polymerization loci.⁴⁵ In fact, GPC traces revealed a sharp peak followed by a broad signal at high MWs, indicating the presence of droplets with very low deactivator concentration ([Figure S1](#)).

Under homogeneous conditions, Cu^I/Me₆TREN⁺ is 1 order of magnitude more reactive than Cu^I/TPMA⁺. Therefore, in miniemulsion the following strategies were attempted to slow down the reaction and improve control with Cu^IMe₆TREN⁺: (i) reduce catalyst and/or ascorbic acid loadings, (ii) use of NaCl instead of NaBr, and (iii) replace the EBiB initiator by MBP, with a secondary less reactive alkyl structure.⁵⁴ Nevertheless, all polymerizations were fast and polymers with high $\bar{D}$ were obtained ([Table S1](#)).

The Cu^IPMDETA⁺ catalyst is much less active than either Cu^IMe₆TREN⁺ or Cu^ITPMA⁺.^{55,56} Therefore, the poor control observed with Br-Cu^{II}PMDETA⁺ suggests that the interaction of this complex with SDS is very weak. In conclusion, pyridinic ligands, such as TPMA, are better suited for miniemulsion ARGET ATRP due to the specific interactions between catalyst and surfactant, which enable both Cu^I and Cu^{II} species to enter the hydrophobic droplets and tune the polymerization process.

Effect of Structure and Amount of Surfactant on Miniemulsion ATRP of BA. Several anionic surfactants were evaluated to form ion-pair complexes ([Scheme 3](#)): SDS, sodium dodecylbenzenesulfonate (SDBS), and sodium dodecanoate (SDA).

SDBS provided a fast polymerization ([Table 2](#), entry 6, and [Figure S2](#)), reaching 84% conversion in 3 h, but polymers with $\bar{D} = 1.32$, higher than with SDS under identical conditions, were obtained. The higher polymerization rate and the decreased control may be caused by a weaker interaction between Br-Cu^{II}TPMA⁺ and SDBS, leading to a lower amount of the Cu^{II} species inside the droplets.

SDA alone could not stabilize the BA miniemulsion; therefore, a combination of SDS and SDA was tested (4.6 wt % SDS + 0.5 wt % SDA relative to BA, [Table 2](#), entry 7, and [Figure S2](#)). The obtained miniemulsion was stable, but particle size increased to ca. 270 nm (almost twice larger than with other surfactants). Polymerization was slightly faster than with SDS alone, yielding polymers with $\bar{D} = 1.25$ and suggesting the

Table 2. Effect of Various Ligand–Surfactant Combinations in ARGET ATRP Miniemulsion Polymerization of BA^a

entry	ligand	surfactant	t (h)	conv (%)	k_p^{app} (h ⁻¹) ^b	$M_{n,\text{app}}$ (×10 ⁻³)	$M_{n,\text{th}}$ (×10 ⁻³)	$\bar{D}$	d_z^c (nm)
1	TPMA	SDS	6	66	0.25	30.9	24.4	1.17	117 ± 2
2	TPMA ^d	SDS	5	70	0.31	24.1	25.5	1.14	152 ± 1
3	TPMA*2	SDS	3	40	0.21	10.0	14.5	1.24	114 ± 1
4	PMDETA	SDS	2	79	1.42	38.5	28.8	5.02	161 ± 1
5	Me ₆ TREN	SDS	1.1	89	2.21	32.4	32.2	2.65	152 ± 2
6	TPMA	SDBS	3	84	0.63	29.8	30.4	1.32	153 ± 1
7	TPMA	SDS + SDA ^e	5	74	0.31	27.4	27.0	1.25	273 ± 3

^aGeneral conditions as in [Table 1](#). [AsAc]/[Cu^{II}] = 0.5, AsAc injected dropwise at $t = 0$ h. ^bThe slope of the $\ln([M]_0/[M])$ vs time plot. ^cZ-average particles diameter, measured by DLS. ^dEt₄NBr replaced NaBr. ^e[SDS] = 4.6 wt % and [SDA] = 0.5 wt % relative to BA.

Table 3. ARGET ATRP Miniemulsion Polymerization of BA with Different Amounts of SDS^a

entry	[SDS] (wt % rel to BA)	<i>t</i> (h)	conv (%)	<i>k</i> _p ^{app} (h ⁻¹)	<i>M</i> _{n,app} (×10 ⁻³)	<i>M</i> _{n,th} (×10 ⁻³)	<i>Đ</i>	<i>d</i> _z ^c (nm)
1	9.2	4	81	0.50	30.2	29.4	1.12	106 ± 2
2	4.6	6	66	0.25	30.9	24.4	1.17	117 ± 2
3	2.3	13	74	0.12	30.2	26.7	1.30	161 ± 1
4	1.15	20	74	0.16	35.2	27.2	1.32	207 ± 2

^aGeneral conditions as in Table 1. [AsAc]/[Cu^{II}] = 0.5, AsAc injected dropwise at *t* = 0 h. ^bThe linear slope of the ln([M]₀/[M]) vs time in the first 10 h of polymerization. ^cZ-average particle diameter measured by DLS.

presence of a different Cu^I/Cu^{II} ratio. SDA seemed to slightly destabilize the system, while SDS ensured the effective interaction with the Cu complex. Therefore, SDA can be used in combination with SDS to tune the particle size but preserving most of the polymerization control and the latex stability.

Finally, the amount of SDS was varied to change latex properties and polymerization kinetics (Table 3 and Figure 1).

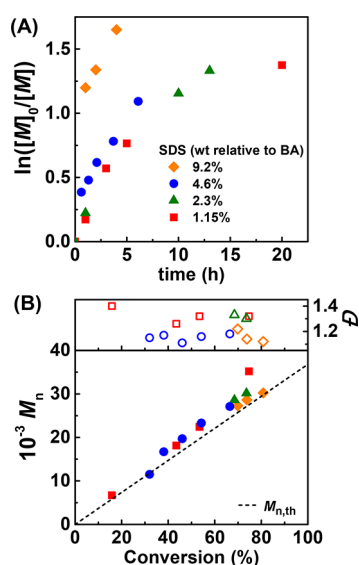


Figure 1. ARGET miniemulsion ATRP of BA with different amounts of SDS (Table 3). (A) Semilogarithmic kinetic plot and (B) MW and *Đ* evolution vs conversion. [AsAc]/[Cu^{II}] = 0.5 added dropwise at *t* = 0 h. Other conditions as in Table 1.

By lowering [SDS], *k*_p^{app} decreased and first-order kinetics deviated from linearity. A controlled polymerization was even obtained with [SDS] as low as 1.15 wt % relative to monomer, which is below the critical micellar concentration (cmc) of the surfactant in the polymerization media (cmc = 8.9 mM for SDS in water + 0.1 M NaBr, *T* = 65 °C, which corresponds to 1.46 wt % relative to BA).⁴⁵ Reducing [SDS] resulted in decreased control because less ion pairs were formed and less catalyst was bound to the surface of the droplets. Polymerization rate decreased because the droplets size increased, lowering the overall interfacial area, which slowed down the kinetics of mass transport. Nevertheless, the process remained controlled (*Đ* = 1.1–1.3) and the final latexes were stable, meaning that the amount of SDS can be varied to tune particles dimensions.

Effect of Catalyst Loading on Miniemulsion ARGET ATRP of BA and BMA. The Br–Cu^{II}TPMA⁺ loading was reduced from 719, to 360, and to 144 ppm in a miniemulsion ARGET ATRP of BA and resulted in maintaining comparable polymerization rates (Table 4 and Figure S4). However, the dispersity increased with decreasing catalyst loading, in agreement with eq 1:^{7,57}

$$\bar{D} = 1 + \left(\frac{k_p[R-X]}{k_{\text{deact}}[X-\text{Cu}^{\text{II}}\text{L}^+]} \right) \left(\frac{2}{p} - 1 \right) \quad (1)$$

where *k*_p is the propagation rate constant, *k*_{deact} is the deactivation rate constant, and *p* is conversion.

Control over BA polymerization was lost when 144 ppm of catalyst were used, which resulted in polymers with *Đ* = 1.65. Conversely, 360 ppm of catalyst ensured a well-controlled polymerization, even if, based on previous analysis, less than 10 ppm of copper species were present inside the monomer droplets under these conditions.⁴⁵

Table 4. ARGET ATRP Miniemulsion Polymerization of BA and BMA with Different Catalyst Loadings and Targeted DP^a

entry	[Br–Cu ^{II} TPMA ⁺] (ppm)	target DP	<i>t</i> (h)	conv (%)	<i>k</i> _p ^{app} (h ⁻¹)	<i>M</i> _{n,app} (×10 ⁻³)	<i>M</i> _{n,th} (×10 ⁻³)	<i>Đ</i>	<i>d</i> _z ^c (nm)
monomer = BA, R–X = EBiB ^d									
1	719	280	6	66	0.25	24.4	30.9	1.17	117 ± 2
2	360	280	4	70	0.34	25.6	34.1	1.24	126 ± 2
3	144	280	4	71	0.31	26.1	36.7	1.65	121 ± 1
4	719	1000	20	71	0.07	91.6	101.8	1.25	126 ± 1
monomer = BMA, R–X = EBPA ^e									
5	800	280	1	82	1.60	36.3	32.9	1.26	135 ± 2
6	200	280	2	90	1.05	36.3	36.1	1.33	132 ± 3
7	50	280	2	77	0.72	31.6	30.9	1.31	139 ± 3
8	800	600	2.5	82	0.52	70.0	70.2	1.20	138 ± 2
9	800	1200	4	76	0.38	118.6	129.3	1.42	131 ± 2
10 ^f	800	280	6	92	0.35	34.5	36.9	1.18	193 ± 1

^aGeneral conditions as in Table 1. ^bThe slope of the ln([M]₀/[M]) vs time plot. ^cZ-average particles diameter by DLS before polymerization.

^d[AsAc]/[Cu^{II}] = 0.5, AsAc injected dropwise at *t* = 0 h. ^e[AsAc]/[Cu^{II}] = 0.4 injected dropwise every 30 min, unless otherwise noted.

^fBr–Cu^{II}BPMODA⁺⁺ was used as catalyst; [AsAc]/[Cu^{II}] = 0.5 injected at *t* = 0 h.

ARGET ATRP of BMA was similar to BA polymerization. In fact, Br–Cu^{II}TPMA⁺ is poorly soluble in either BA or BMA (Figure S5), and therefore it entered monomer droplets only when paired with SDS.

ARGET ATRP of BMA required careful selection of the initiator: tertiary alkyl halides, such as EBiB, are less efficient initiators for methacrylates due to the penultimate unit effect.⁵⁸ Indeed, with EBiB polymerization was slow resulting in polymers with $\bar{D} = 1.35$ (Figure S6). Instead, ethyl 2-bromophenylacetate (EBPA), which is much more reactive than EBiB,^{59,60} provided a well-controlled process, reaching 34% conversion in 2 h and polymers with $\bar{D} = 1.13$ (Table S2).

Polymerization stopped after 2 h, suggesting that the initial addition of AsAc ([AsAc]/[Br–Cu^{II}TPMA⁺] = 0.5) did not provide continuous regeneration of the active catalyst. Hence, the feeding of AsAc was optimized as described in the Supporting Information (Table S2 and Figure S8); a fast and well-controlled polymerization was obtained by simply injecting 0.4 equivalents of AsAc with respect to initial Br–Cu^{II}TPMA⁺, at $t = 0$ h and then subsequently every 30 min. 82% conversion in 1 h and polymers with $\bar{D} = 1.26$ were obtained, with good agreement between experimental and theoretical MWs (Table 4, entry 5, and Figure 2).

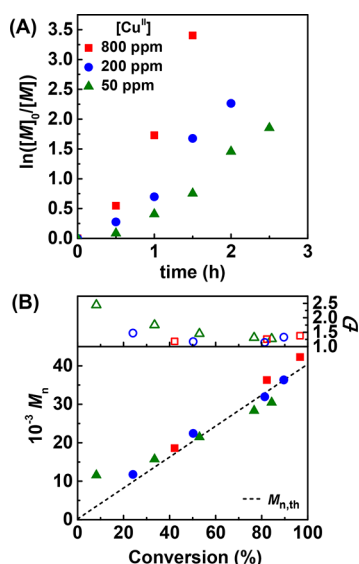


Figure 2. Miniemulsion ARGET ATRP of BMA with various catalyst loadings. (A) Semilogarithmic kinetic plot and (B) MW and $\bar{D}$ evolution vs monomer conversion. [AsAc]/[Cu^{II}] = 0.4, injected dropwise every 30 min. Other reaction conditions are listed in Table 1.

Catalyst loading was successfully reduced from 800 to 50 ppm in ARGET ATRP of BMA (Table 4, entries 5–7). Polymerization rate (R_p) decreased with decreasing amount of Cu, exhibiting a good proportionality between R_p and the square root of [Br–Cu^{II}TPMA⁺], as predicted from eq 2:⁶¹

$$R_p = k_p^{\text{app}}[M] = k_p[M][P^*] = k_p[M]\sqrt{\frac{k_{\text{red}}[\text{AsAc}][\text{Br-Cu}^{\text{II}}\text{TPMA}^+]}{2k_t}} \quad (2)$$

where k_{red} is the reduction rate constant of Br–Cu^{II}TPMA⁺ and k_t is the termination rate constant. 50 ppm of Br–Cu^{II}TPMA⁺, corresponding to 6.25×10^{-5} M, provided 77% conversion in 2 h with a final polymer with $\bar{D} = 1.31$. However, $\bar{D}$ was higher during the first hour due to the slow ATRP deactivation with

very low catalyst loadings (Figure 2). The much lower propagation rate constant, k_p , of BMA than of BA permitted good control and low dispersity with few ppm of catalyst (cf. eq 1).⁶²

Interestingly, the polymerization rate of BMA varied with initial [Cu^{II}], while the polymerization rate of BA did not. This is likely due to the different extent of radical termination in the two systems. The BMA system, with high ATRP activity and lower k_p , was characterized by higher radical concentration, which increased the extent of radical termination. Therefore, a large portion of Cu^I catalyst was regenerated, and the kinetics agreed with eq 2. In the BA system, on the contrary, radical concentration was lower and termination was almost negligible. In this case, addition of AsAc established a fixed [Cu^I]/[Cu^{II}] ratio, so that the kinetics did not depend on [Cu^{II}]. (Note that a constant [AsAc]/[Cu^{II}] was used in each case.)

ICP-MS measurements of the precipitated PBMA revealed residual copper contents as low as 4.5, 1.6, and 0.3 ppm, with initial catalyst loadings of respectively 800, 200, and 50 ppm (over the total amount of monomer). Less than 1% of the initial copper content remained in the final polymer after precipitation. Metal contamination in the ppb range makes the polymer suitable for some applications without any purification procedure.⁶³

For comparison, ARGET ATRP of BMA in miniemulsion was carried out with a traditionally used hydrophobic complex (Table 4, entry 10, and Figure S7), namely BPMODA*, which was specifically designed to form a highly active and hydrophobic copper catalyst.⁴⁹ BPMODA* was prepared as described in the Supporting Information. Under the same conditions used for Cu/TPMA, Cu/BPMODA* gave well-controlled polymers, but particles size was 80% larger, suggesting potential destabilization of the droplets' surface.⁴³ Starting from 800 ppm of Br–Cu^{II}BPMODA*, ICP-MS measurements determined 45 ppm of residual copper in the precipitated polymer, 10 times higher than with Br–Cu^{II}TPMA⁺/SDS.

Effect of Targeted DP on Miniemulsion ATRP of BA and BMA. Higher degrees of polymerization were targeted by lowering initiator concentration. PBA with DP > 700, $\bar{D} = 1.25$, and good agreement between theoretical and experimental MWs was obtained. Polymerization rate decreased for lower [R–X], as expected from eq 2, due to lower amount of generated radicals (Table 4, entry 4).⁶¹

High-MW PBMA was obtained when targeting DP = 600 and 1200 (Table 4, entries 8 and 9). Once again, polymerization rates were proportional to [R–X]. By switching from targeted DP = 280 to 600, $\bar{D}$ diminished from 1.25 to 1.20, in agreement with eq 1. However, $\bar{D}$ increased to 1.42 for DP = 1200 (Figure 3A), possibly due to the high viscosity in the polymerizing droplets. An increase of viscosity, besides slowing down termination events, can hamper radical deactivation by the small amount of Cu^{II} present inside the droplets. High viscosity can be related to the “autoacceleration” of the polymerization after 2 h (Figure 3A), which was concomitant with the increase in dispersity (Figure 3B).

Chain Extension Experiments. To test chain-end fidelity of the obtained polymers, a PBMA-MI was prepared by miniemulsion ARGET ATRP with Br–Cu^{II}TPMA⁺/SDS (see details in the Supporting Information). After purification, the macroinitiator had $M_{n,\text{app}} = 4000$ and $\bar{D} = 1.31$ (Figure S10). Chain extension polymerizations were performed with both BA (Table 5, entry 1) and *tert*-butyl methacrylate (*t*BMA, Table 5,

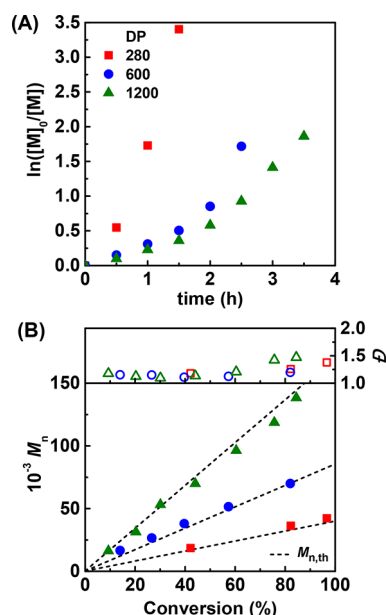


Figure 3. Miniemulsion ARGET of BMA with different target D with different target DPs (280, 600 and 1200). (A) Kinetic plot and (B) MW and D vs monomer conversion. $[AsAc]/[Cu^{II}] = 0.5$. Other reaction conditions listed in Table 1.

entry 2). Figures 4A and 4B show a clean shift of MWs in both cases, with monomodal MW distributions, confirming the high retention of chain-end functionality in the first block. The second block was also well-controlled, with $D_2 = 1.34$ for *t*BMA and $D_2 = 1.15$ for BA, calculated as $D - 1 = w_1^2(D_1 - 1) + w_2^2(D_2 - 1)$, where w_1 and w_2 are the weight fractions of the first and second block, respectively.⁶⁴ Thus, PBMA-MI was successfully chain-extended with both methacrylates and acrylates. High chain-end fidelity, indicating well-controlled polymerizations, motivated the synthesis of more complex structures by miniemulsion ARGET ATRP, such as star and brush-like polymers.

Synthesis of Polymer Stars. PBA and PBMA stars were prepared by grafting from a β -cyclodextrin core that was functionalized with 14 ATRP initiators (β -CD-Br₁₄).⁶⁵ The structure of β -CD-Br₁₄ is illustrated in Scheme 3, while its synthesis is described in the Supporting Information. A clean shift of MW was observed in the GPC traces during the “grafting from” polymerizations with both BA and BMA (Figure 4C,D). PBA star polymers were well-defined (Table 5, entry 3), with $M_{n,app} < M_{n,th}$ since the hydrodynamic volume of a star polymer is lower than its linear analogue with the same

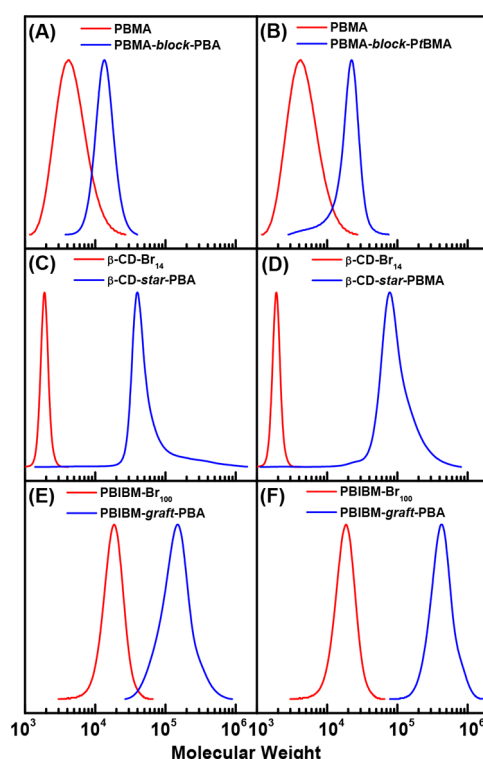


Figure 4. GPC traces of polymers with different architectures, prepared by ARGET miniemulsion ATRP. Chain extensions of PBMA-MI with (A) *t*BMA and (B) BA; multiarm star polymers from β -CD-Br₁₄ macroinitiator and (C) BA or (D) BMA; PBA molecular brushes with DP target (E) 25 and (F) 100. Detailed conditions are listed in Table 5.

MW.⁶⁵ The formation of the PBMA star polymer was less controlled (Table 5, entry 4).

Synthesis of Polymer Brushes. Molecular brushes were successfully prepared in a miniemulsion by grafting BA from a poly(2-(2-bromoisobutyryloxy)ethyl methacrylate) (PBiBM₁₀₀) macroinitiator, comprising a methacrylate backbone functionalized with ca. 100 α -bromoisobutyrate initiating sites. The structure of PBiBM₁₀₀ is illustrated in Scheme 3. Successful synthesis of molecular brushes requires minimal termination to avoid coupling between the multifunctional macromolecules. Indeed, direct injection of AsAc at the beginning of the reaction produced too many radicals and resulted in coupled chains, i.e., gelation (Figure S11A). Therefore, the concentration of radicals was lowered by (i) decreasing SDS concentration (cf. Table 3) and (ii) gradually feeding AsAc to the reaction in order to slowly reduce Cu^{II} to the activator Cu^I state (Table 5, entries 5

Table 5. Preparation of Polymers with Complex Structures by ARGET ATRP in Miniemulsion^a

entry	initiator	polymer	<i>t</i> (h)	conv (%)	k_p^{app} (h ⁻¹)	$M_{n,app}$ (×10 ⁻³)	$M_{n,th}$ (×10 ⁻³)	D	d_z^c (nm)
1 ^d	PBMA-Br	PBMA- <i>block</i> -PBA	2	30	0.20	13.0	11.7	1.10	118 ± 1
2 ^e	PBMA-Br	PBMA- <i>block</i> -P <i>t</i> BMA	1	30	0.35	16.1	12.6	1.19	119 ± 1
3 ^e	β -CD-Br ₁₄	β -CD- <i>star</i> -PBA	2	73	0.70	47.7	65.7	1.39	118 ± 2
4 ^e	β -CD-Br ₁₄	β -CD- <i>star</i> -PBMA	2	76	0.95	82.2	78.1	1.54	138 ± 2
5 ^f	PBiBM ₁₀₀	PBiBM ₁₀₀ - <i>graft</i> -PBA	4	94	0.44	357	125	1.29	194 ± 2
6 ^f	PBiBM ₁₀₀	PBiBM ₁₀₀ - <i>graft</i> -PBA	7	57	0.15	775	347	1.28	155 ± 1

^aGeneral conditions: monomer 20 vol % in H₂O + 0.1 M NaBr, $T = 65^\circ\text{C}$; $V_{tot} = 10\text{ mL}$, $[Cu^{II}Br_2/TPMA] = 1\text{ mM}$, $[SDS] = 4.6\text{ wt \%}$, $[hexadecane] = 10.8\text{ wt \%}$ relative to monomer. ^bThe slope of the $\ln([M]_0/[M])$ vs time plot. ^cZ-average particle diameter by DLS before polymerization. ^dAsAc feeding rate = 3 $\mu\text{mol/h}$. ^eAsAc feeding rate = 2 $\mu\text{mol/h}$. ^fAsAc feeding rate = 50 nmol/h and $[SDS] = 2.3\text{ wt \%}$ relative to monomer.

and 6). Slightly larger particles were obtained according to DLS, as expected from the lower C_{SDS} , but the final miniemulsion was stable and no gelation was observed. Molecular brushes with side-chain length of DP = 24 and 57 were prepared. In both cases, radical termination by coupling was minimal, according to the low intensity of high MW shoulders in the GPC traces (Figure 4E,F). Again, $M_{n,app}$ was lower than $M_{n,th}$ due to the very compact nature of molecular brushes.

3. CONCLUSION

The interaction between hydrophilic catalysts and SDS provided ion-pair and interfacial catalysts suitable for controlled ARGET ATRP of BA, BMA, and *t*BMA in a miniemulsion polymerization. The setup was simple, with the use of commercially available reagents to prepare *in situ* a $Br-Cu^{II}TPMA^+/DS^-$ ion-pair complex, followed by reduction with ascorbic acid to activate the polymerization.

The final latexes contained very low amount of residual copper, possibly avoiding the need for any further purification. Indeed, the hydrophilic $Br-Cu^{II}TPMA^+$ complex migrated to the aqueous phase when crashing the miniemulsion by dilution. Low dispersity PBMA was obtained by lowering Cu loading to 50 ppm, which resulted in 300 ppb Cu in the final latex. Residual copper content was 10 times lower than when using traditional hydrophobic complexes.

High degrees of polymerization were successfully targeted with both BA and BMA. Moreover, chain extension of a PBMA macroinitiator showed excellent retention of chain-end functionality. Monomodal block copolymers PBMA-*block*-PBA and PBMA-*block*-PtBMA with $\bar{D} < 1.2$ were formed in few hours. Well-defined star and brush polymers were also prepared, showing minimal radical termination by coupling.

Compared to traditional superhydrophobic catalysts, miniemulsion ATRP by interfacial and ion-pair catalysis employs commercially available reagents, readily affording polymers with high purity. The hydrophilic ion-pair catalysts can also potentially be used with water-soluble or amphiphilic initiating systems, opening new avenues for controlled polymerizations in dispersed media that are currently being investigated.

■ ASSOCIATED CONTENT

Supporting Information

The Supporting Information is available free of charge on the ACS Publications website at DOI: 10.1021/acs.macromol.7b01730.

Characterization of aqueous phase catalysts and additional polymerization results (PDF)

■ AUTHOR INFORMATION

Corresponding Author

*(K.M.) E-mail km3b@andrew.cmu.edu.

ORCID

Yi Wang: 0000-0002-4002-9516

Paweł Chmielarczyk: 0000-0002-9101-6264

Abdirisak A. Isse: 0000-0003-0966-1983

Armando Gennaro: 0000-0002-7665-7178

Krzysztof Matyjaszewski: 0000-0003-1960-3402

Author Contributions

Y.W. and F.L. contributed equally.

Notes

The authors declare no competing financial interest.

■ ACKNOWLEDGMENTS

The support from the National Science Foundation (CHE 1707490) and the National Institutes of Health (R01DE020843) is acknowledged. F. Lorandi acknowledges Fondazione Aldo Gini. P. Chmielarczyk acknowledges Kosciuszko Foundation Fellowship. The authors acknowledge Xiaoyu Gao for the kind help in ICP-MS tests and Guojun Xie for the preparation of PBiBM₁₀₀ macroinitiator and useful discussions.

■ REFERENCES

- (1) Zetterlund, P. B.; Kagawa, Y.; Okubo, M. Controlled/Living Radical Polymerization in Dispersed Systems. *Chem. Rev.* **2008**, *108*, 3747–3794.
- (2) Jennings, J.; He, G.; Howdle, S. M.; Zetterlund, P. B. Block Copolymer Synthesis by Controlled/Living Radical Polymerisation in Heterogeneous Systems. *Chem. Soc. Rev.* **2016**, *45*, 5055–5084.
- (3) Cunningham, M. F. Controlled/Living Radical Polymerization in Aqueous Dispersed Systems. *Prog. Polym. Sci.* **2008**, *33*, 365–398.
- (4) Wu, M.; Ramirez, L. M. F.; Lozano, A. R.; Quemener, D.; Babin, J.; Durand, A.; Marie, E.; Six, J. L.; Nouvel, C. First Multi-Reactive Dextran-Based Inisurf for Atom Transfer Radical Polymerization in Miniemulsion. *Carbohydr. Polym.* **2015**, *130*, 141–148.
- (5) Saade, J.; Bordes, C.; Raffin, G.; Hangouet, M.; Marote, P.; Faure, K. Response Surface Optimization of Miniemulsion: Application to UV Synthesis of Hexyl Acrylate Nanoparticles. *Colloid Polym. Sci.* **2016**, *294*, 27–36.
- (6) Wu, L.; Glebe, U.; Boker, A. Synthesis of Hybrid Silica Nanoparticles Densely Grafted with Thermo and pH Dual-Responsive Brushes via Surface-Initiated ATRP. *Macromolecules* **2016**, *49*, 9586–9596.
- (7) Matyjaszewski, K. Atom Transfer Radical Polymerization (ATRP): Current Status and Future Perspectives. *Macromolecules* **2012**, *45*, 4015–4039.
- (8) Moad, G.; Rizzardo, E.; Thang, S. H. Living Radical Polymerization by the RAFT Process - A Third Update. *Aust. J. Chem.* **2012**, *65*, 985–1076.
- (9) Nicolas, J.; Guillauneuf, Y.; Lefay, C.; Bertin, D.; Giges, D.; Charleux, B. Nitroxide-Mediated Polymerization. *Prog. Polym. Sci.* **2013**, *38*, 63–235.
- (10) Airaud, C.; Heroguez, V.; Gnanou, Y. Bicompartimentalized Polymer Particles by Tandem ROMP and ATRP in Miniemulsion. *Macromolecules* **2008**, *41*, 3015–3022.
- (11) Airaud, C.; Ibarboure, E.; Gaillard, C.; Heroguez, V. Nanostructured Polymer Composite Nanoparticles Synthesized in a Single Step via Simultaneous ROMP and ATRP Under Microemulsion Conditions. *J. Polym. Sci., Part A: Polym. Chem.* **2009**, *47*, 4014–4027.
- (12) Min, K.; Matyjaszewski, K. Atom Transfer Radical Polymerization in Aqueous Dispersed Media. *Cent. Eur. J. Chem.* **2009**, *7*, 657–674.
- (13) Sun, J. T.; Hong, C. Y.; Pan, C. Y. Recent Advances in RAFT Dispersion Polymerization for Preparation of Block Copolymer Aggregates. *Polym. Chem.* **2013**, *4*, 873–881.
- (14) Cao, J.; Zhang, L. F.; Jiang, X. W.; Tian, C.; Zhao, X. N.; Ke, Q.; Pan, X. Q.; Cheng, Z. P.; Zhu, X. L. Facile Iron-Mediated Dispersant-Free Suspension Polymerization of Methyl Methacrylate via Reverse ATRP in Water. *Macromol. Rapid Commun.* **2013**, *34*, 1747–1754.
- (15) Li, Z.; Chen, W. J.; Zhang, Z. B.; Zhang, L. F.; Cheng, Z. P.; Zhu, X. L. A Surfactant-Free Emulsion RAFT Polymerization of Methyl Methacrylate in a Continuous Tubular Reactor. *Polym. Chem.* **2015**, *6*, 1937–1943.
- (16) Kagawa, Y.; Zetterlund, P. B.; Minami, H.; Okubo, M. Compartmentalization in Atom Transfer Radical Polymerization (ATRP) in Dispersed Systems. *Macromol. Theory Simul.* **2006**, *15*, 608–613.

- (17) Zetterlund, P. B.; Okubo, M. Compartmentalization in Nitroxide-Mediated Radical Polymerization in Dispersed Systems. *Macromolecules* **2006**, *39*, 8959–8967.
- (18) Thomson, M. E.; Cunningham, M. F. Compartmentalization Effects on the Rate of Polymerization and the Degree of Control in ATRP Aqueous Dispersed Phase Polymerization. *Macromolecules* **2010**, *43*, 2772–2779.
- (19) Wang, J. S.; Matyjaszewski, K. Controlled Living Radical Polymerization - Atom-Transfer Radical Polymerization in the Presence of Transition-Metal Complexes. *J. Am. Chem. Soc.* **1995**, *117*, 5614–5615.
- (20) De Paoli, P.; Isse, A. A.; Bortolamei, N.; Gennaro, A. New Insights Into the Mechanism of Activation of Atom Transfer Radical Polymerization by Cu(I) Complexes. *Chem. Commun.* **2011**, *47*, 3580–3582.
- (21) Simakova, A.; Averick, S. E.; Konkolewicz, D.; Matyjaszewski, K. Aqueous ARGET ATRP. *Macromolecules* **2012**, *45*, 6371–6379.
- (22) Payne, K. A.; D'hooge, D. R.; van Steenberge, P. H. M.; Reyniers, M. F.; Cunningham, M. F.; Hutchinson, R. A.; Marin, G. B. ARGET ATRP of Butyl Methacrylate: Utilizing Kinetic Modeling to Understand Experimental Trends. *Macromolecules* **2013**, *46*, 3828–3840.
- (23) Matyjaszewski, K.; Jakubowski, W.; Min, K.; Tang, W.; Huang, J. Y.; Braunecker, W. A.; Tsarevsky, N. V. Diminishing Catalyst Concentration in Atom Transfer Radical Polymerization with Reducing Agents. *Proc. Natl. Acad. Sci. U. S. A.* **2006**, *103*, 15309–15314.
- (24) Matyjaszewski, K.; Tsarevsky, N. V.; Braunecker, W. A.; Dong, H.; Huang, J.; Jakubowski, W.; Kwak, Y.; Nicolay, R.; Tang, W.; Yoon, J. A. Role of Cu⁰ in Controlled/"Living" Radical Polymerization. *Macromolecules* **2007**, *40*, 7795–7806.
- (25) Zhang, Y.; Wang, Y.; Matyjaszewski, K. ATRP of Methyl Acrylate with Metallic Zinc, Magnesium, and Iron as Reducing Agents and Supplemental Activators. *Macromolecules* **2011**, *44*, 683–685.
- (26) Konkolewicz, D.; Wang, Y.; Krys, P.; Zhong, M. J.; Isse, A. A.; Gennaro, A.; Matyjaszewski, K. SARA ATRP or SET-LRP. End of controversy? *Polym. Chem.* **2014**, *5*, 4396–4417.
- (27) Williams, V. A.; Matyjaszewski, K. Expanding the ATRP Toolbox: Methacrylate Polymerization with an Elemental Silver Reducing Agent. *Macromolecules* **2015**, *48*, 6457–6464.
- (28) Williams, V. A.; Ribelli, T. G.; Chmielarz, P.; Park, S.; Matyjaszewski, K. A Silver Bullet: Elemental Silver as an Efficient Reducing Agent for Atom Transfer Radical Polymerization of Acrylates. *J. Am. Chem. Soc.* **2015**, *137*, 1428–1431.
- (29) Bortolamei, N.; Isse, A. A.; Magenau, A. J. D.; Gennaro, A.; Matyjaszewski, K. Controlled Aqueous Atom Transfer Radical Polymerization with Electrochemical Generation of the Active Catalyst. *Angew. Chem., Int. Ed.* **2011**, *50*, 11391–11394.
- (30) Magenau, A. J. D.; Strandwitz, N. C.; Gennaro, A.; Matyjaszewski, K. Electrochemically Mediated Atom Transfer Radical Polymerization. *Science* **2011**, *332*, 81–84.
- (31) Park, S.; Chmielarz, P.; Gennaro, A.; Matyjaszewski, K. Simplified Electrochemically Mediated Atom Transfer Radical Polymerization using a Sacrificial Anode. *Angew. Chem., Int. Ed.* **2015**, *54*, 2388–2392.
- (32) Lorandi, F.; Fantin, M.; Isse, A. A.; Gennaro, A. Electrochemically Mediated Atom Transfer Radical Polymerization of *n*-Butyl Acrylate on Non-platinum Cathodes. *Polym. Chem.* **2016**, *7*, 5357–5365.
- (33) Chmielarz, P.; Fantin, M.; Park, S.; Isse, A. A.; Gennaro, A.; Magenau, A. J. D.; Sobkowiak, A.; Matyjaszewski, K. Electrochemically Mediated Atom Transfer Radical Polymerization (eATRP). *Prog. Polym. Sci.* **2017**, *69*, 47–78.
- (34) Konkolewicz, D.; Schroder, K.; Buback, J.; Bernhard, S.; Matyjaszewski, K. Visible Light and Sunlight Photoinduced ATRP with ppm of Cu Catalyst. *ACS Macro Lett.* **2012**, *1*, 1219–1223.
- (35) Pan, X. C.; Tasdelen, M. A.; Laun, J.; Junkers, T.; Yagci, Y.; Matyjaszewski, K. Photomediated Controlled Radical Polymerization. *Prog. Polym. Sci.* **2016**, *62*, 73–125.
- (36) Mohapatra, H.; Kleiman, M.; Esser-Kahn, A. P. Mechanically Controlled Radical Polymerization Initiated by Ultrasound. *Nat. Chem.* **2016**, *9*, 135–139.
- (37) Wang, Z. H.; Pan, X. C.; Yan, J. J.; Dadashi-Silab, S.; Xie, G. J.; Zhang, J. N.; Wang, Z. H.; Xia, H. S.; Matyjaszewski, K. Temporal Control in Mechanically Controlled Atom Transfer Radical Polymerization Using Low ppm of Cu Catalyst. *ACS Macro Lett.* **2017**, *6*, 546–549.
- (38) Tayal, A.; Kelly, R. M.; Khan, S. A. Rheology and Molecular Weight Changes During Enzymatic Degradation of a Water-Soluble Polymer. *Macromolecules* **1999**, *32*, 294–300.
- (39) Paik, H. J.; Kickelbick, G.; Matyjaszewski, K. Immobilization of the Copper Catalyst in Atom-Transfer Radical Polymerization. *Macromolecules* **1999**, *32*, 2941–2947.
- (40) Matyjaszewski, K.; Pintauer, T.; Gaynor, S. Removal of Copper-Based Catalyst in Atom Transfer Radical Polymerization Using Ion Exchange Resins. *Macromolecules* **2000**, *33*, 1476–1478.
- (41) Gromada, J.; Spanswick, J.; Matyjaszewski, K. Synthesis and ATRP Activity of New TREN-Based Ligands. *Macromol. Chem. Phys.* **2004**, *205*, 551–566.
- (42) Jasinski, N.; Lauer, A.; Stals, P. J. M.; Behrens, S.; Essig, S.; Walther, A.; Goldmann, A. S.; Barner-Kowollik, C. Cleaning the Click: A Simple Electrochemical Avenue for Copper Removal from Strongly Coordinating Macromolecules. *ACS Macro Lett.* **2015**, *4*, 298–301.
- (43) Wei, Y. P.; Zhang, Q.; Wang, W. J.; Li, B. G.; Zhu, S. P. Improvement on Stability of Polymeric Latexes Prepared by Emulsion ATRP Through Copper Removal Using Electrolysis. *Polymer* **2016**, *106*, 261–266.
- (44) Tsarevsky, N. V.; Matyjaszewski, K. Green" Atom Transfer Radical Polymerization: From Process Design to Preparation of Well-Defined Environmentally Friendly Polymeric Materials. *Chem. Rev.* **2007**, *107*, 2270–2299.
- (45) Fantin, M.; Chmielarz, P.; Wang, Y.; Lorandi, F.; Isse, A. A.; Gennaro, A.; Matyjaszewski, K. Harnessing the Interaction between Surfactant and Hydrophilic Catalyst To Control eATRP in Miniemulsion. *Macromolecules* **2017**, *50*, 3726–3732.
- (46) Min, K.; Gao, H. F.; Matyjaszewski, K. Preparation of Homopolymers and Block Copolymers in Miniemulsion by ATRP Using Activators Generated by Electron Transfer (AGET). *J. Am. Chem. Soc.* **2005**, *127*, 3825–3830.
- (47) Kagawa, Y.; Minami, H.; Okubo, M.; Zhou, H. Preparation of Block Copolymer Particles by Two-Step Atom Transfer Radical Polymerization in Aqueous Media and Its Unique Morphology. *Polymer* **2005**, *46*, 1045–1049.
- (48) Simms, R. W.; Cunningham, M. E. High Molecular Weight Poly(Butyl Methacrylate) via ATRP Miniemulsions. *Macromol. Symp.* **2008**, *261*, 32–35.
- (49) Elsen, A. M.; Burdyska, J.; Park, S.; Matyjaszewski, K. Active Ligand for Low PPM Miniemulsion Atom Transfer Radical Polymerization. *Macromolecules* **2012**, *45*, 7356–7363.
- (50) Fantin, M.; Park, S.; Wang, Y.; Matyjaszewski, K. Electrochemical Atom Transfer Radical Polymerization in Miniemulsion with a Dual Catalytic System. *Macromolecules* **2016**, *49*, 8838–8847.
- (51) Min, K.; Yu, S.; Lee, H. I.; Mueller, L.; Sheiko, S. S.; Matyjaszewski, K. High Yield Synthesis of Molecular Brushes via ATRP in Miniemulsion. *Macromolecules* **2007**, *40*, 6557–6563.
- (52) Teo, V. L.; Davis, B. J.; Tsarevsky, N. V.; Zetterlund, P. B. Successful Miniemulsion ATRP Using an Anionic Surfactant: Minimization of Deactivator Loss by Addition of a Halide Salt. *Macromolecules* **2014**, *47*, 6230–6237.
- (53) Fantin, M.; Isse, A. A.; Gennaro, A.; Matyjaszewski, K. Understanding the Fundamentals of Aqueous ATRP and Defining Conditions for Better Control. *Macromolecules* **2015**, *48*, 6862–6875.
- (54) Tang, W.; Matyjaszewski, K. Effect of Ligand Structures on Activation Rate Constants in ATRP. *Macromolecules* **2007**, *40*, 1858–1863.
- (55) Tang, W.; Kwak, Y.; Braunecker, W.; Tsarevsky, N. V.; Coote, M. L.; Matyjaszewski, K. Understanding Atom Transfer Radical

Polymerization: Effect of Ligand and Initiator Structures on the Equilibrium Constants. *J. Am. Chem. Soc.* **2008**, *130*, 10702–10713.

(56) Fantin, M.; Isse, A. A.; Bortolamei, N.; Matyjaszewski, K.; Gennaro, A. Electrochemical Approaches to the Determination of Rate Constants for the Activation Step in Atom Transfer Radical Polymerization. *Electrochim. Acta* **2016**, *222*, 393–401.

(57) Mastan, E.; Zhu, S. P. A Molecular Weight Distribution Polydispersity Equation for the ATRP System: Quantifying the Effect of Radical Termination. *Macromolecules* **2015**, *48*, 6440–6449.

(58) Nanda, A. K.; Matyjaszewski, K. Effect of Penultimate Unit on the Activation Process in ATRP. *Macromolecules* **2003**, *36*, 8222–8224.

(59) Jakubowski, W.; Matyjaszewski, K. Activators Regenerated by Electron transfer for Atom-Transfer Radical Polymerization of (Meth)Acrylates and Related Block Copolymers. *Angew. Chem., Int. Ed.* **2006**, *45*, 4482–4486.

(60) Tang, W.; Matyjaszewski, K. Effects of Initiator Structure on Activation Rate Constants in ATRP. *Macromolecules* **2007**, *40*, 1858–1863.

(61) Krys, P.; Matyjaszewski, K. Kinetics of Atom Transfer Radical Polymerization. *Eur. Polym. J.* **2017**, *89*, 482–523.

(62) Beuermann, S.; Buback, M.; Davis, T. P.; Gilbert, R. G.; Hutchinson, R. A.; Kajiwar, A.; Klumperman, B.; Russell, G. T. Critically Evaluated Rate Coefficients for Free-Radical Polymerization, 3. Propagation Rate Coefficients for Alkyl Methacrylates. *Macromol. Chem. Phys.* **2000**, *201*, 1355–1364.

(63) Egorova, K. S.; Ananikov, V. P. Which Metals are Green for Catalysis? Comparison of the Toxicities of Ni, Cu, Fe, Pd, Pt, Rh, and Au Salts. *Angew. Chem., Int. Ed.* **2016**, *55*, 12150–12162.

(64) Fukuda, T.; Goto, A. Gel Permeation Chromatographic Determination of Activation Rate Constants in Nitroxide-controlled Free Radical Polymerization, 2. Analysis of Evolution of Polydispersities. *Macromol. Rapid Commun.* **1997**, *18*, 683–688.

(65) Chmielarz, P.; Park, S.; Sobkowiak, A.; Matyjaszewski, K. Synthesis of Beta-Cyclodextrin-Based Star Polymers via a Simplified Electrochemically Mediated ATRP. *Polymer* **2016**, *88*, 36–42.