

Article

Polysiloxane/Polystyrene Thermo-Responsive and Self-Healing Polymer Network via Lewis Acid-Lewis Base Pair Formation

Fernando Vidal ¹, Huina Lin ¹, Cecilia Morales ¹, and Frieder Jäkle ^{1,*}

¹ Department of Chemistry, Rutgers University-Newark, 73 Warren Street, Newark, New Jersey 07102, United States; fer.vidal@rutgers.edu (F. V.); hl519@scarletmail.rutgers.edu (H. L.); cecialmorales@gmail.com (C. M.)

* Correspondence: fjaekle@newark.rutgers.edu; Tel.: +1-973-353-5064

Received: date; Accepted: date; Published: date

Abstract: The use of thermo-reversible Lewis Pair (LP) interactions in the formation of transient polymer networks is still greatly underexplored. In this work, we describe the synthesis and characterization of polydimethylsiloxane/polystyrene (PDMS/PS) blends that form dynamic Lewis acid-Lewis base adducts resulting in reversible crosslinks. Linear PS containing 10 mol% of di-2-thienylboryl pendant groups randomly distributed was obtained in a two-step one-pot functionalization reaction from silyl-functionalized PS, while ditelechelic PDMS with pyridyl groups at the chain-termini was directly obtained via thiol-ene “click” chemistry from commercially available vinyl-terminated PDMS. The resulting soft gels, formed after mixing solutions containing the PDMS and PS polymers, behave at room temperature as elastomeric solid-like materials with very high viscosity (47300 Pa·s). We applied rheological measurements to study the thermal and time dependence of the viscoelastic moduli, and also assessed the reprocessability and self-healing behavior of the dry gel.

Keywords: boron; Lewis acid; transient polymer networks; organoborane; supramolecular polymers; telechelic polymers; organoboron polymers; self-healing.

1. Introduction

The use of non-covalent bonds in the construction of advanced supramolecular networks has brought about an ever increasing diversity of polymeric elastomers and soft gels [1-5], which possess very promising applications as stimuli-responsive [6,7], mechanochromic [8], self-repairing [9-11], shape-memory [12], and controlled-release [13] materials. It is the combination of fixed covalent bonds within the polymer chains and the dynamic nature of transient supramolecular crosslinks that provides these materials with interesting mechanical properties and features of both irreversible thermosets (permanently crosslinked, rubbery and elastic) and easily reprocessable and recyclable viscoelastic polymer melts [5,14]. Indeed, supramolecular interactions based on hydrogen-bonding [15-19], π - π stacking [20], inclusion complexation [21], metal-ligand [22-24], and ionic interactions [25] have been extensively exploited in the reversible crosslinking of polymers.

A relatively much less explored strategy involves Lewis pair (LP) interactions between Lewis acid and Lewis base functionalities as a tool for the formation of reversible supramolecular polymers and networks. As in the case of other non-covalent bonds, an equilibrium is established between the free Lewis acids/bases and the LP adducts. The nature of this equilibrium is determined by the relative Lewis acid and Lewis base strength, which in turn depends on both steric and electronic effects, and can be shifted by changes in temperature and concentration [26,27]. The facile functionalization of molecular and polymeric materials with borane Lewis acid groups makes boron-

containing building blocks particularly attractive [28–32]. For instance, the group of Severin has investigated Lewis base-functionalized boronate esters, in particular catecholboranes, in the supramolecular self-assembly of extended networks from small molecule precursors [33,34]. However, the resulting organogels require the use of solvents and are relatively weak materials due to the lack of true polymeric viscous flow [35,36]. More recently, Brook and coworkers mixed two complementary polydimethylsiloxane (PDMS) polymers, one containing aryl-boronate esters as Lewis acid and the other primary alkyl amines as Lewis base, to form the first example of thermoreversible crosslinked silicones via non-covalent LP interactions [37]. The formation of materials with alternatively low viscosity, elastomeric, and brittle characteristics was accomplished by relatively small changes in the crosslinking density. Finally, Shaver and coworkers elegantly used non-interacting arylborane- and dimesitylphosphine-bearing polystyrene (PS) to generate thermoresponsive and self-healing organogels by adding dynamic steric “frustration” to the LP interactions and forcing the transient network to form by activation of a small molecule [38].

In this study, we explored whether LP interactions placed at the interface of two immiscible, but complementary polymers—one carrying the LA, the other carrying the LB—could be exploited to render a homogeneously dispersed and thermoreversible supramolecular polymer network (Figure 1). This strategy would obviate the need for external compatibilizers to stabilize the dispersion, such as block-copolymers additives [39]. Ditelechelic PDMS functionalized with Lewis basic pyridine groups at the chain termini provides flexible and low-melting bridging strands required for the viscous flow of the gel at room temperature. A PS random copolymer containing pendant Lewis acidic organoborane moieties in turn serves as multifunctional crosslinker. Our investigations reveal a dramatic impact of the reversible Lewis acid-base interactions (B–N bond formation) on the transient polymer network thus formed, which exhibits elastomeric, thermo-responsive, and self-healing characteristics.

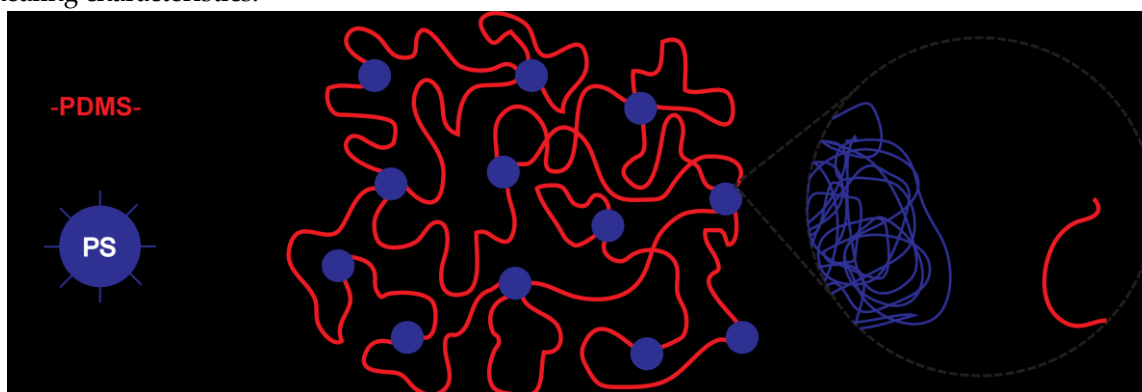



Figure 1. Schematic representation of the proposed crosslinked supramolecular network in the PS/PDMS blend promoted by Lewis-acid/Lewis-base pairs (LA = Lewis acid, LB = Lewis base).

2. Results and Discussion

2.1. Synthesis of LA/LB Containing Polymers and Adduct Formation

The synthesis of linear *soft* polymers carrying the Lewis base pyridine (**PDMS-PY**) at the chain termini was achieved by thiol-ene “click” reaction between commercially available vinyl-terminated polydimethylsiloxane (DP ~ 67, determined by ^1H NMR) and pyridylethyl mercaptan (Scheme 1). Complete olefin conversion was achieved with only a moderate excess of the mercaptan (3 equivalents per vinyl group), as shown by the total disappearance of the $-\text{CH}=\text{CH}_2$ resonances (*dd* centered at $\delta = 6.12$, 5.93, and 5.73 ppm) in the ^1H NMR spectrum (Figure 2). Formation of new thioether bonds was quantitative in the presence of 2,2'-azobis(2-methylpropionitrile) (AIBN) in toluene at 65 °C for 15 hours, also confirmed by the new aromatic signals (doublets centered at $\delta = 8.52$, and 7.14 ppm for **PDMS-PY**) and ethylene signals (centered at $\delta = 2.88$, 2.79, 2.60, and 0.90 ppm for **PDMS-PY**) in the ^1H NMR of the isolated polymer (Figure 2). A single precipitation in methanol was sufficient to remove all excess reagents from the isolated product. The final LB-content as

established by ^1H NMR end-group analysis was 0.8 mol% for **PDMS-PY**, which is somewhat lower than the vinyl content (1.5 mol%) in the parent PDMS. Moreover, gel permeation chromatography (GPC) analysis of the isolated polymer showed a significant increase in the polymer number average molecular weight (M_n) from 5,400 Da of the commercial sample to 9,600 Da of the pyridyl-functionalized PDMS, which is more than what could be accounted for with only the new added end-groups (Figure S1,a). These discrepancies, together with a decrease in the molecular weight dispersity (D) from 1.74 to 1.26 and the less than quantitative recovery, can be explained by the loss of a small soluble fraction of PDMS oligomers during the MeOH washing step. Finally, MALDI-TOF analysis of a low molecular weight sample of **PDMS-PY** ($DP \sim 12$) obtained under otherwise identical conditions further supports the structure of the telechelic polymers (Figure S2). First, the difference between peaks ($\Delta = 74.02 \text{ m/z}$) corresponds to the mass of the PDMS repeating unit ($-\text{SiMe}_2\text{O}-$), and second, the experimental peak at $m/z = 1226.62$ and the isotopic distribution simulated for a molecular formula of $\text{C}_{42}\text{H}_{96}\text{O}_{11}\text{Si}_{12}\text{N}_2\text{S}_2\text{Na}$ (the sum of the masses for 11 repeat units, the chain-end groups, and Na) matched with an error of less than 4.5 ppm.

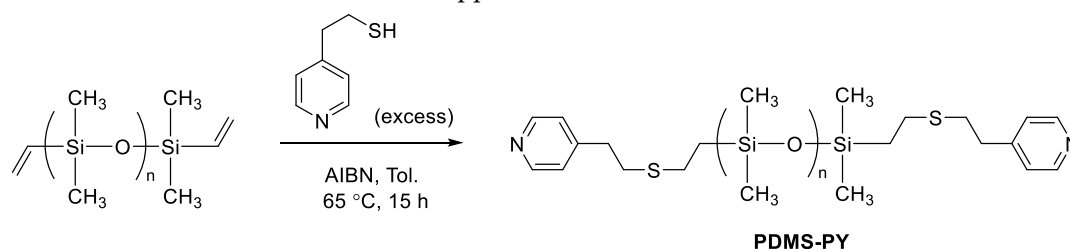

Scheme 1. One-step synthesis of pyridine-bearing telechelic PDMS (**PDMS-PY**) from commercially available vinyl-terminated PDMS.


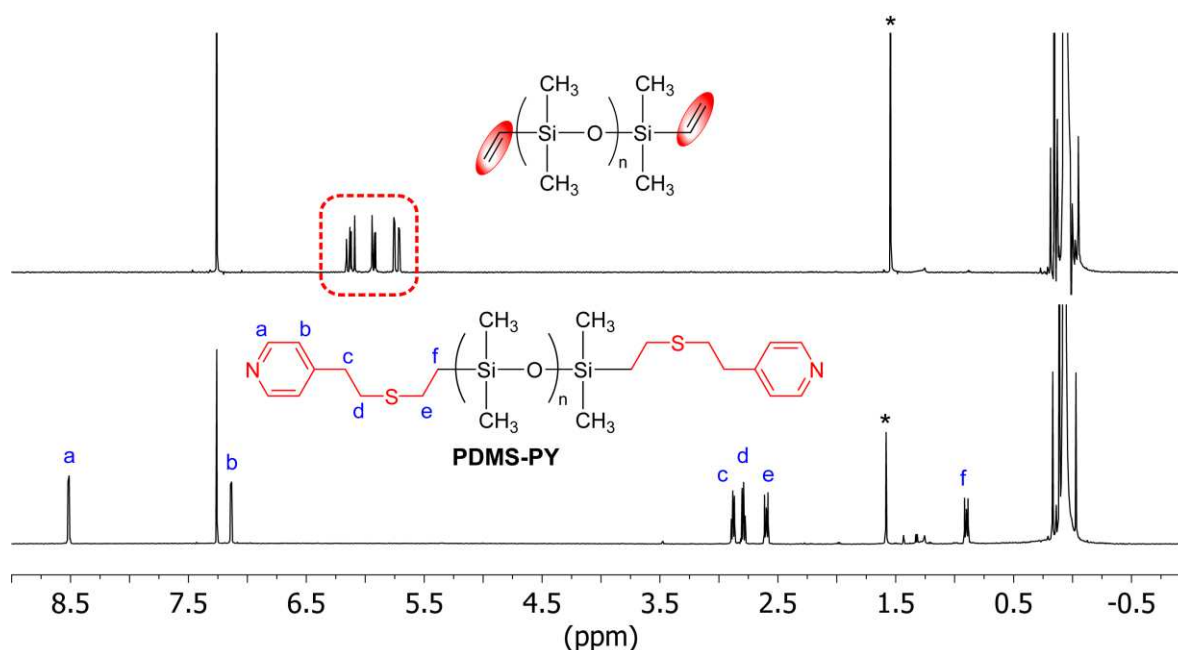


Figure 2. ^1H NMR spectra comparison (25 °C, CDCl_3) of vinyl-terminated telechelic PDMS commercial sample (top), and after installation of pyridyl end-group (**PDMS-PY**, bottom) via “click” reaction. (* = H_2O trace from “wet” CDCl_3).

We employed atom-transfer radical polymerization (ATRP) conditions for the controlled and large-scale synthesis of the polystyrene-based random copolymer precursor, **PS-co-PSTMS**, containing 10 mol% of $-\text{SiMe}_3$ pendant groups (Scheme 2). The ratio of PS to PS-TMS in the isolated product (n:m) matched well the monomer feed ratio, as determined by ^1H NMR (see experimental description). The selective exchange of the trimethylsilyl groups with BBr_3 and subsequent substitution of Br with thiophene groups was achieved by following efficient procedures previously

developed in our group [40,41]. Thus, linear polystyrene, **PS-co-PSBTh**, containing 10 mol% of randomly distributed di-2-thienylboryl pendant groups was conveniently obtained in high yield (81%) via a two-step one-pot reaction from the TMS-functionalized precursor. ^1H NMR analysis of the isolated polymer product showed complete conversion of the TMS groups (disappearance of the $-\text{SiMe}_3$ signal at 0.31 ppm, Figure S3), while new resonances indicated the formation of the substituted organoboron moieties (7.97, 7.81, 7.40 ppm for the dithienylborane groups in **PS-co-PSBTh**, Figure S5). Peak integrations were consistent with a 10 mol% boron content in the final product as described in detail in the experimental section and SI.

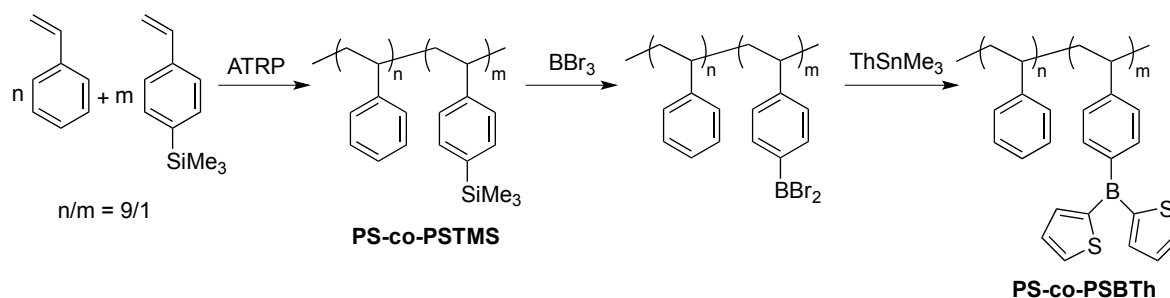

Scheme 2. Synthesis of linear PS-based random copolymer containing 10 mol% of Lewis acidic organoboron moieties with pendant thienyls (**PS-co-PSBTh**).

The ^{11}B NMR spectrum of the isolated **PS-co-PSBTh** showed a single broad peak centered at 52 ppm, which is characteristic of an intact tricoordinated boron center (Figure 3). To study the formation of LA/LB pairs between the highly Lewis acidic pendant boron groups and a Lewis base, the stoichiometric reaction between one equivalent of pyridine and **PS-co-PSBTh** was performed. The ^{11}B NMR of the resulting mixture showed a dramatic upfield shift to 0 ppm ($\Delta\delta = 52$ ppm), indicating that the equilibrium in solution is mostly pushed to the formation of the LA·LB adduct. Indeed, addition of excess 5 equivalents of pyridine did not appreciably change the chemical shift, further demonstrating that the boron is vastly tetracoordinated with only one equivalent of pyridine. The presence of only 10 mol% of boron centers per PS-chain ensured that the polymer·LB adduct remained soluble in C_6D_6 , as opposed to a previously characterized **PSBTh** homopolymer which immediately precipitated [26].

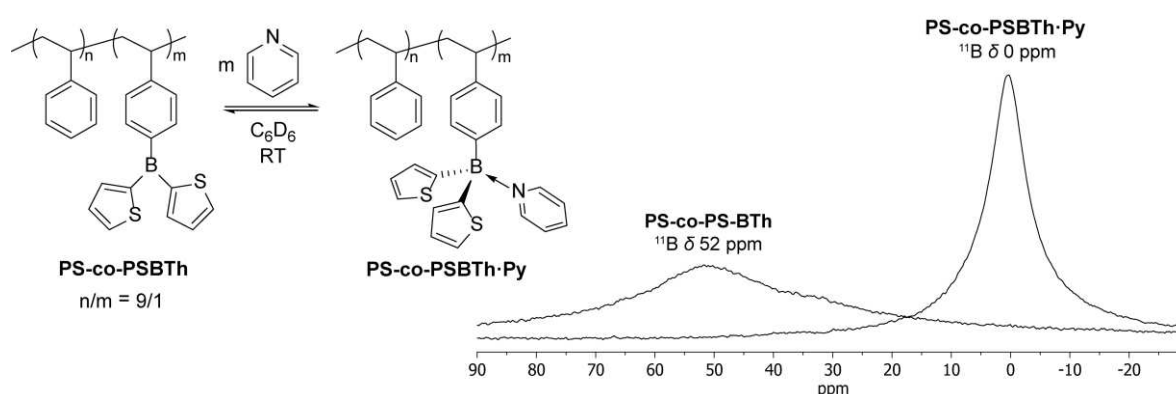


Figure 3. Stoichiometric reaction between **PS-co-PS-BTh** and pyridine and resulting ^{11}B NMR spectra.

2.2. Preparation of PDMS/PS Gel Formulation and Physical Characterization

PDMS/PS blends were conveniently prepared at room temperature by mixing solutions of **PDMS-PY** (~12 wt% in toluene) and **PS-co-PSBTh** (~5 wt% in CH_2Cl_2) in stoichiometric ratios. Upon contact with the PS solution, the PDMS instantaneously underwent crosslinking, which resulted in a heterogeneous gel that separated from the solvent mixture. This clearly suggests that the proposed pyridine-borane adduct formation (Figure 1), also exemplified by the NMR scale reaction (*vide supra*),

readily occurred imposing a non-ordered structure with a high concentration of crosslinking points. However, the dynamic nature of the Lewis pair bond should allow for reorganization of the network to a more favorable thermodynamic structure upon disassociation/association of the pyridine-boron bonds. Indeed, the disordered network spontaneously relaxed in a matter of minutes at room temperature and produced a viscous transparent organogel that could flow (Figure 4, a). Moreover, heating the mixture at 80 °C for one hour generated a perfectly homogeneous and transparent viscous organogel (note that the viscosity changed with solvent content), enabled by the thermal reversibility of the crosslinks and rearrangement of the PDMS/PS network (Figure 4, b). Finally, the volatiles were allowed to slowly evaporate undisturbed over a period of three days, yielding a transparent and almost colorless rubbery gel, **PY-PSBTh** (Figure 4, c), that would not flow after reversing the scintillation vial. In sharp contrast, a control experiment in which **PDMS-PY** was mixed with **PS-co-PSTMS**, containing no boron centers, under identical conditions yielded a heterogeneous mixture of liquid PDMS macroscopically separated from white portions of PS as a consequence of the well-known immiscibility of the two polymers [39,42-44]. The drastic difference in polymer miscibility highlights the importance of the LA/LB pairs to ensure the homogeneous dispersion of PS, which accounts for 11 wt% of the total gel mass, in the PDMS domains.

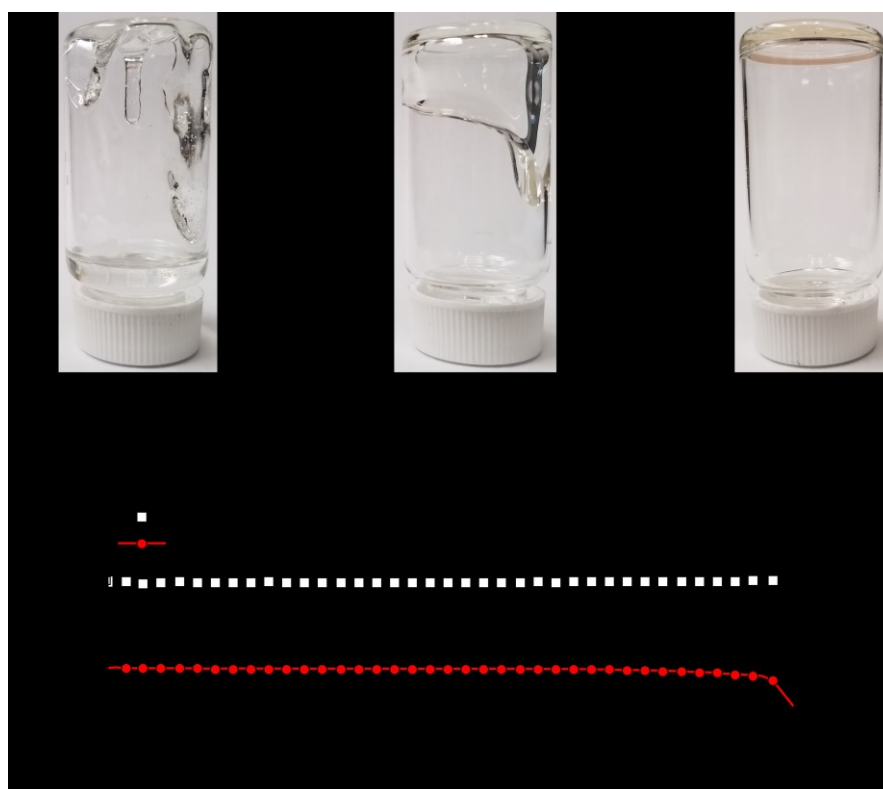


Figure 4. Photographs of **PY-PSBTh** physical blend: (a) soon after the PDMS/PS toluene solutions are mixed (notice the solvent phase separated from the organogels); (b) homogeneous and viscous organogel after annealing at 80 °C for 1 hour; and (c) final PDMS/PS blend after solvent evaporation, **PY-PSBTh**. (d) Strain sweep (100 rad/s at 25 °C) of **PY-PSBTh** dry gel (d).

The solid-like nature of the **PY-PSBTh** xerogel at room temperature was confirmed by oscillatory rheological measurements. A strain-sweep experiment at a frequency of 100 rad/s showed that the storage modulus (elastic component, G') is over an order of magnitude larger than the loss modulus (viscous component, G'') at all the strains tested before breaking (Figure 4, d). Thus, the $G' > G''$ in the linear viscoelastic region indicates that the internal structure at room temperature is in fact that of a highly crosslinked elastomer, which can resist strains greater than 10% even at such high frequencies. Moreover, the zero-shear viscosity (η_0), determined as the complex viscosity (η^*) at low shear-rates (Figure S7), is much higher (47300 Pa·s) compared to that of the free-flowing parent vinyl-

terminated PDMS (0.1 Pa·s). Remarkably, the molecular weight of the **PDMS-PY** employed in this study ($M_n = 9,620$ Da) was well below the critical molecular weight of PDMS (reported at $M_c = 34,500$ Da, approximate DP > 400, [45]); therefore, we can postulate that the rheological observations are not due to the entanglement of the linear PDMS chains, but mostly the reversible crosslinks between the PDMS/PS in the form of Lewis pairs.

Next, the thermal reversibility of the B-N crosslinks in the **PY-PSBTh** blends, already observed qualitatively during the annealing of the organogels, was more accurately studied by heating the solvent-free gel samples at a constant ramp rate (1 °C/min), frequency (1 rad/s), and strain amplitude (1%). The obtained oscillatory rheological data was plotted versus temperature (Figure 5, a). The results showed a marked decrease in G' on going from 0 °C to 70 °C, consistent with a visual softening of the gels, until it reached a crossover temperature ($T_{\text{cross}} = 39.7$ °C) at which $G' = G''$. As we continued heating the sample past the T_{cross} , the rheological response was dominated by the viscous modulus and the gel was able to flow ($G' < G''$). Importantly, a subsequent cooling cycle overlapped well with the heating ramp and the gel could recover previous values of the viscoelastic moduli at low temperatures, effectively regaining its solid-like behavior (Figure S8). Worth noting here is that the rheological experiments were conducted while exposed to air, thus demonstrating also the good stability of the organoborane moieties to high temperatures and oxygen in the presence of the pyridine end-groups.

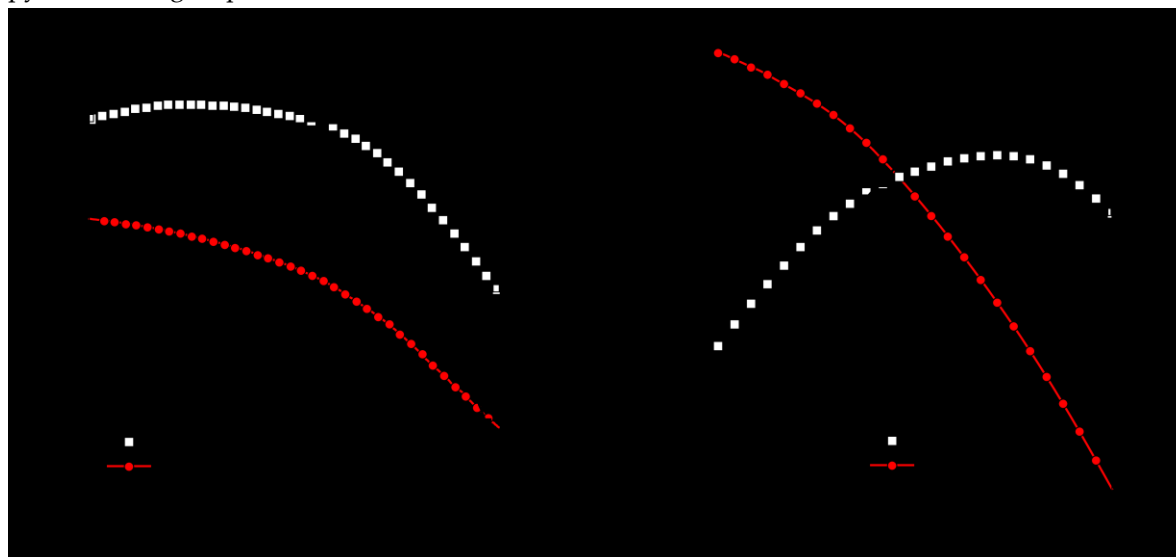


Figure 5. Logarithmic plots of storage modulus (G' , black squares), loss modulus (G'' , white squares), and complex viscosity (η^* , red circles) of **PY-PSBTh** dry gel versus (a) temperature (1 °C/min on heating, 1% strain, and 1 rad/s), and (b) angular frequency (25 °C, 1% strain).

Another important feature of transient networks composed of reversible bonds is the time-dependence of the elastic and viscous moduli with respect to the frequency of the applied stress. Thus, we performed dynamic frequency sweeps at 25 °C and the result of the viscoelastic parameters were plotted versus angular frequency (Figure 5, b). As expected, both the elastic and viscous moduli changed with frequency, and underwent crossover ($G' = G''$) at 0.144 rad/s. This result clearly highlights the reversibility of the crosslinked network: while the gel behaved like an elastic solid at higher frequencies, i.e. the stresses were applied faster than the time needed for the reorganization of the crosslinks, the gel could flow at lower frequencies since the breaking/making of the B-N bonds occurred on a similar time-scale as the stress. Moreover, the crossover frequency, ω_c , is directly related to the relaxation time, τ , of the viscoelastic network, where $\tau = 2\pi/\omega_c$. Thus, the relaxation time of **PY-PSBTh**, i.e. the average time required to relax by the elastic nodes of the network, was calculated to be 44 s at room temperature.

Thermal characterization of **PY-PSBTh** by differential scanning calorimetry (DSC) only evidenced a prominent melting transition at −48 °C, which can be assigned to the PDMS domains (Figure S9). In contrast, a glass transition for the PS domains (T_g of parent **PS-co-PSBTh** = 118.3 °C)

was not detected nor could be any other thermal transition associated with a crosslinking/decrosslinking reaction, possibly due to the relatively small number of Lewis acid-base pairs. Finally, the thermal stability of the gel, as established by thermal gravimetric analysis (TGA), can be correlated with the mass content of its component: it showed a two-step decomposition profile, with a first onset decomposition temperature, $T_{\text{onset},1}$, at 363 °C that accounted for the weight percent of the PS-domains, and a second decomposition temperature, $T_{\text{onset},2}$, at 480 °C corresponding to the PDMS-domains (Figure S10, a). The maxima of the decomposition steps in the first derivative trace overlapped well with the decomposition maxima of the parent polymers (Figure S10, b), hence supporting this assignment.

2.3. Observation of Self-Healing Properties

The easy access to the flowing regimes and relative short relaxation times at room temperature for **PY-PSBTh** suggest that this material should be suitable for reprocessability and may display self-healing properties. Indeed, a sample of pulverized **PY-PSBTh** that was allowed to rest undisturbed at room temperature and under no stress, except for that from gravity, was able to almost completely recover the bulk shape within a week (Figure 6). Even larger gaps were “healed” after standing for an extra week, and the gel almost occupied the volume of the vial. Clearly, by allowing the disassociation of the crosslinks, the PDMS chains could slowly flow so that the soft domains could blend together through the ruptured pieces and reform the network structure. This process could be accelerated at 70 °C, where it took about 1 hour to rebuild the network by effectively melting the sample. This is another indication of the transient nature of the B-N crosslinks, which otherwise would not allow the reformation of the gel material.



Figure 6. Photographs of solid **PY-PSBTh** broken xerogel (b) and reconstituted **PY-PSBTh** after standing at room temperature for 1 week (c), 2 weeks (d), and heating at 70 °C for 1 hour (a).

3. Materials and Methods

3.1. General Considerations

All oxygen- and moisture-sensitive manipulations were carried out under an inert atmosphere using either standard Schlenk techniques on a dual-manifold Schlenk line or a N₂-filled glovebox. NMR data were acquired at 25 °C on a 500 MHz Bruker AVANCE spectrometer (499.9 MHz ¹H, 125.7 MHz ¹³C, 160.4 MHz ¹¹B, and 470.4 MHz ¹⁹F) or on a Varian INOVA 600 MHz spectrometer (599.7 MHz ¹H, 150.8 MHz ¹³C, 192.4 MHz ¹¹B, and 564.3 MHz ¹⁹F). ¹¹B NMR spectra were acquired with boron-free quartz NMR tubes either on the Varian INOVA 600 with a boron-free 5 mm dual broadband gradient probe (Nalorac, Varian Inc., Martinez, CA) or the 500 MHz Bruker Auto Avance with a 5mm PH SEX 500S1 11B-H/F-D probe. ¹H and ¹³C spectra were referenced internally to solvent signals and all other NMR spectra externally to SiMe₄ (0 ppm); chemical shifts are reported as parts per million relative to SiMe₄.

Boron tribromide, N,N,N',N'',N''-pentamethyldiethylenetriamine (PMDETA), pyridine, and 2,2'-azobis(2-methylpropionitrile) (AIBN) were purchased from Sigma-Aldrich. Copper(II) bromide and 2-phenylethyl bromide were purchased from Acros Organics. Vinyl-terminated polydimethylsiloxane ($M_n = 5,400$ Da, $\bar{D} = 1.74$, 1.5 mol% of vinyl groups) was purchased from Gelest. The following compounds were prepared according to published procedures: 4-trimethylsilylstyrene [46–48], 2-trimethylstannylthiophene [49], and 2-(pyridin-4-yl)ethane-1-thiol [50]. 4-

Trimethylsilylstyrene and pyridine were dried over CaH₂, vacuum distilled, and degassed via several freeze-pump-thaw cycles prior to use.

MALDI-TOF MS analyses were performed on a Bruker Ultraflex extreme in linear mode. Anthracene (10 mg/mL) was used as the matrix and mixed with the samples (10 mg/mL in DCM) in a 1:1 ratio, and then spotted on the wells of a target plate. Red phosphorus was used for calibration. GPC analyses were performed using a Viscotek GPCmax equipped with a VE 2001 GPC solvent/sample module, a 2600 PDA detector, a TDA 305 triple detector array, and a column set consisting of a PLgel 5 mm mixed-D and two PLgel 5 mm mixed-C columns. The system was calibrated against narrow polystyrene standards (10) in the molecular weight range of 580 to 371100 Da.

3.2. Syntheses and Characterizations

3.2.1. Synthesis of Poly(styrene-co-4-trimethylsilylstyrene), PS-co-PSTMS.

The random copolymer precursor poly(styrene-co-4-trimethylsilylstyrene), **PS-co-PSTMS**, was prepared by atom transfer radical polymerization (ATRP) of styrene and 4-trimethylsilylstyrene in 9:1 molar ratio respectively. This procedure was adapted from that of the corresponding poly-(4-trimethylsilylstyrene) homopolymer [40,41]. Inside of a N₂-filled glovebox, 3.61 g (0.019 mol) of phenyl ethyl bromide, 2.80 g (0.019 mol) of CuBr, 68.80 g (0.39 mol) of freshly distilled 4-trimethylsilylstyrene, and 365.7 g (3.51 mol) of freshly distilled styrene were added to a Schlenk flask and the mixture was diluted with anhydrous anisole (200 mL). The reaction flask was interfaced to a dual-manifold Schlenk line and the solution degassed with a slow stream of dry N₂ for 30 min. Then, 3.38 g (0.019 mol) of PMDETA were quickly transferred via syringe. The polymerization mixture was immersed in a 110 °C oil-bath and vigorously stirred for 5 hours. The reaction was terminated by placing the flask on ice. The mixture was then filtered through a short plug of neutral alumina and the filter was repeatedly washed with THF. The combined organic phases were concentrated and precipitated in a large excess of MeOH. Reprecipitation of the product into MeOH was repeated three times from the smallest amount of THF needed. Finally, the product was precipitated into hexanes and dried under vacuum at 100 °C overnight to yield a white powder. The ratio of PS to PS-TMS in the product (n:m) was determined by integration of the peaks in the ¹H NMR for the PS/PS-TMS (overlapping peaks centered at 6.57 ppm for the 2,6-aryl H's) compared to PS-TMS (centered at 0.31 ppm for the SiMe₃ exclusively). Yield = 372 g (85%). *M_n* = 16.4 kDa, *D* = 1.62. n:m = 9:1 (10 mol% in TMS groups). *T_g* = 103.4 °C.

¹H NMR (499.9 MHz, CDCl₃, 25 °C): δ 7.14 (br s, PS *m,p*-aryl and PS-TMS 2,6-aryl overlapped), 6.63–6.52 (br s, PS *o*-aryl and PS-TMS 3,5-aryl overlapped), 2.26–1.90 (br, PS and PS-TMS –CH₂CH– overlapped), 1.50 (br, PS and PS-TMS –CH₂CH– overlapped), 0.31 (s, SiMe₃). ¹³C NMR (150.8 MHz, CDCl₃, 25 °C): 145.8 (br, PS 1-aryl), 137.1, 136.8 (PS-TMS 1-aryl and 4-aryl), 133.2 (br, PS-TMS 3,5-aryl), 128.1 (br, PS and PS-TMS 2,6-aryl, overlapped), 127.8 (br, PS 3,5-aryl), 125.8 (br, PS 4-aryl) 47–42 (br, –CH₂CH–), 40.5 (br, –CH₂CH–), –0.77 (SiMe₃).

3.2.2. Synthesis of Poly(styrene-co-4-(di-2-thienylboryl)styrene), PS-co-PSBTh.

The “one-pot” synthesis of polystyrene random copolymer containing 10 mol% of di-2-thienylboryl units, **PS-co-PSBTh**, was adapted from the synthesis of the corresponding borane homopolymer [40]. *Caution:* BBr₃ is toxic and highly corrosive! Inside of a N₂-filled glovebox, a solution of BBr₃ (0.82 g, 3.27 mmol) in 10 mL of dry CH₂Cl₂ was added dropwise at room temperature to a stirring solution of **PS-co-PSTMS** (3.00 g, 2.69 mmol of TMS groups) in 20 mL of dry CH₂Cl₂. After the addition was completed, the solution was allowed to stir at room temperature for 24 hours. ¹H NMR analysis of a reaction aliquot showed complete replacement of the TMS groups for –BBr₂. Subsequently, a solution of 2-(trimethylstannyl)thiophene (1.66 g, 6.72 mmol) in 5 mL of dry CH₂Cl₂ was added at room temperature, and the reaction mixture was stirred overnight. The reaction solution was concentrated under vacuum to 5 mL, and the polymer was recovered by repeated precipitation from toluene into hexanes. The resulting off-white solid was washed with hexanes and

dried under high vacuum at 50 °C overnight to give a white powder. The ratio of PS to PS-BTh in the product (n:m) was determined by integration of the peaks in the ^1H NMR for the PS/PS-BTh (overlapping peaks centered at 7.10 ppm) compared to PS-BTh (centered at 7.40 ppm for the 4-Th H's). Yield: 2.60 g (79%). $M_n = 19.0$ kDa, $\bar{D} = 1.20$. n:m = 9:1 (10 mol% in B-thiophene groups). $T_g = 118.3$ °C.

^1H NMR (499.9 MHz, CDCl_3 , 25 °C): δ 7.97 (br s, PS-BTh 5-Th), 7.81 (br s, PS-BTh 3-Th), 7.53 (br s, PS-BTh 2,6-aryl), 7.40 (br s, PS-BTh 4-Th), 7.10 (br s, PS *m,p*-aryl and PS-BTh 3,5-aryl overlapped), 6.65 (br s, PS *o*-aryl), 1.93 (br, PS and PS-BTh $-\text{CH}_2\text{CH}-$ overlapped), 1.49 (br, PS and PS-BTh $-\text{CH}_2\text{CH}-$ overlapped). ^{13}C NMR (150.8 MHz, CDCl_3 , 25 °C): 148.4 (br, PS-BTh 4-aryl), 145.7 (br, PS 1-aryl), 145.2 (PS-BTh 2-Th), 142.5 (PS-BTh 3-Th), 140.6 (br, PS-BTh 1-aryl), 137.1 (PS-BTh 5-Th), 129.0 (PS-BTh 4-Th), 128.1 (br, PS and PS-BTh 2,6-aryl, overlapped), 127.8 (br, PS 3,5-aryl), 126.9 (br, PS-BTh 3,5-aryl), 125.8 (br, PS 4-aryl) 47–42 (br, $-\text{CH}_2\text{CH}-$), 40.6 (br, $-\text{CH}_2\text{CH}-$). ^{11}B NMR (160.4 MHz, C_6D_6 , 25 °C): δ 52 ppm (broad).

3.2.3. Reaction of **PS-co-PSBTh** with Pyridine.

PS-co-PSBTh (45.4 mg, 0.037 mmol of LA) was dissolved in 0.4 mL of C_6D_6 . To this solution, an equimolar amount of pyridine (2.9 mg, 0.037 mmol) in 0.2 mL of C_6D_6 was added at room temperature with a syringe from a stock solution. Both solutions were mixed vigorously, transferred to a quartz (boron-free) NMR tube and analyzed by NMR.

^1H NMR (499.9 MHz, C_6D_6 , 25 °C): δ 8.36 (br s, Py), 7.36–6.73 (br s, PS-BTh and PS aryl H's, overlapped), 6.27 (br s, Py), 2.11 (br, PS and PS-BTh $-\text{CH}_2\text{CH}-$ overlapped), 1.62 (br, PS and PS-BTh $-\text{CH}_2\text{CH}-$ overlapped). ^{11}B NMR (160.4 MHz, C_6D_6 , 25 °C): δ 0 ppm (broad).

3.2.4. Synthesis of Pyridine-Terminated Telechelic PDMS, **PDMS-PY**.

The procedure was adapted from a previously published method for a “click” side-chain modification of PDMS with 2-(pyridin-4-yl)ethane-1-thiol [50]. Inside of a N_2 -filled glovebox, a high-pressure glass vessel containing a magnetic stir bar was loaded with 10.01 g of vinyl-terminated telechelic PDMS (2.02 mmol of vinyl groups) and diluted with 15 mL of toluene. Then, AIBN (198 mg, 1.20 mmol) and 2-(pyridin-4-yl)ethane-1-thiol (1.68 mg, 12.08 mmol) were added, the vessel was tightly closed and the mixture stirred at 65 °C in an oil bath for 15 h. After cooling down to room temperature, the reaction mixture was filtered to remove any small particles and slowly precipitated over vigorously stirring MeOH (500 mL). The high molecular weight fraction of the polymer was isolated by centrifugation followed by decanting of the MeOH supernatant, washed with fresh MeOH (2×50 mL), and finally dried under high vacuum at 50 °C until no MeOH peaks were detected in the ^1H NMR spectrum (the lower molecular weight fraction was discarded from the MeOH wash). The isolated pyridine-terminated telechelic PDMS was a colorless oil, soluble in most organic solvents (including hexanes). Yield = 7.05 g (70%). Pyridyl content = 0.8 mol%. $M_n = 9.60$ kDa, $\bar{D} = 1.27$. $T_m = -48.1$ °C, -38.0 °C.

^1H NMR (499.9 MHz, CDCl_3 , 25 °C): δ 8.51 (d, $J = 5.0$ Hz, py H's, chain-end), 7.14 (d, $J = 4.0$ Hz, py H's, chain-end), 2.88 (t, $J = 6.2$ Hz, py- CH_2- , chain-end), 2.79 (m, $-\text{CH}_2\text{SCH}_2-$, chain-end), 2.60 (m, $-\text{CH}_2\text{SCH}_2-$, chain-end), 0.90 (t, $J = 6.7$ Hz, $-\text{Si}(\text{CH}_3)_2\text{CH}_2-$, chain-end), 0.07 (s, $-\text{OSi}(\text{CH}_3)_2-$, main-chain).

3.2.5. Procedure for the Preparation of Gel Formulations.

The blends of PDMS/PS polymers were prepared as follows. Inside a N_2 -filled glovebox, a 20 mL scintillation vial was charged with 500 mg of **PDMS-PY** (0.050 mmol of LB) and dissolved in 4 mL of toluene. Separately, an equimolar amount of **PS-co-PSBTh** (66 mg, 0.050 mmol of LA) was dissolved in 1 mL of CH_2Cl_2 . The PS-copolymer solution was quickly transferred via pipette at room temperature, upon which the PDMS solution in toluene immediately gelled. The gel/solvent mixture was capped, vigorously shaken, and placed in a heated bath at 80 °C for 1 hour, after which a homogeneous viscous liquid was formed. The vial was equilibrated at room temperature, uncapped,

and allowed to slowly evaporate undisturbed at room temperature for 3 days. At this point, the residual volatiles were removed under vacuum from the obtained gels at room temperature for 2 hours.

3.2.6. Rheology Measurements

Oscillatory shear measurements were performed on a Discovery HR-2 rheometer (TA Instruments) with sandblasted 25 mm parallel plates. Gels were loaded onto a thermally regulated Peltier plate with a clean spatula at 70 °C to remove the thermomechanical history of the polymer blends. Axial force was allowed to relax while taking the geometry gap to 400 µm (trim gap of 425 µm). Dynamic tests were performed in the viscoelastic linear region after performing dynamic strain sweeps at 25 °C after 15 min of equilibration (100 rad/s, 0.01-100% strain). Dynamic stress sweeps (10-200,000 µN.m, 100 points per decade) were run at a frequency of 1.0 rad/s to determine the zero shear viscosity. Dynamic temperature tests were run at a ramp rate of 1 °C/min from 70 °C to 0 °C with a strain of 1% and a frequency of 1.0 rad/s. The crossover temperature is reported from the heating ramp, repeated immediately after the first cooling ramp and with the same experimental parameters. A second cooling ramp from 70 °C to 0 °C was performed with the same experimental parameters. Dynamic frequency sweeps (100 to 0.001 rad/s, 10 points per decade) were recorded at 25 °C after 15 min of equilibration with a strain of 1%. Data analysis was carried out with the TRIOS Software Version 4.2.1 (TA Instruments).

4. Conclusions

We disclose a novel strategy to construct transient polymer networks by blending together two immiscible linear polymers that are functionalized with complementary Lewis acid and Lewis base groups, rendering perfectly air-stable, homogeneous, and transparent solid-like gels. The Lewis pair formation between highly Lewis acidic organoboron moieties, in the form of 10 mol% of pendant di-2-thienylboryl pendant groups attached to PS chains, and Lewis basic pyridine groups attached at the chain termini of ditelechelic PDMS, provide critical thermo-reversible crosslinking points. The latter impart viscoelastic properties as demonstrated by thermal and rheological characterizations, as well as reprocessability and self-healing qualities. Our results further suggest vast opportunities for tuning the properties of transient networks by judiciously selecting the strength of the Lewis-acid/Lewis-base interactions and the creation of new thermoplastic elastomers with self-healing properties, a subject we are currently investigating.

Supplementary Materials: Supporting Figures S1 to S10 are available at www.mdpi.com/link.

Acknowledgments: This material is based upon work supported by the National Science Foundation under Grant CHE-1609043 and Rutgers University under SEED grant 202607. The Bruker 500 MHz NMR spectrometer used in this study was supported by an NSF-MRI grant (No. CHE-1229030) and the Polymer and Nanomaterials Facility at Rutgers University Newark by the New Jersey Higher Education Equipment Leasing Fund (ELF III 047-04).

Author Contributions: “F.V. and F.J. conceived and designed the experiments; F.V., H.L., and C.M. synthesized the polymers; F.V. performed the experiments and analyzed the data; F.V. and F.J. wrote and edited the paper.”

Conflicts of Interest: The authors declare no conflict of interest.

References

1. Piepenbrock, M.-O.M.; Lloyd, G.O.; Clarke, N.; Steed, J.W. Metal- and anion-binding supramolecular gels. *Chem. Rev.* **2010**, *110*, 1960-2004, DOI: 10.1021/cr9003067.
2. Aida, T.; Meijer, E.W.; Stupp, S.I. Functional supramolecular polymers. *Science* **2012**, *335*, 813-817, DOI: 10.1126/science.1205962.
3. Voorhaar, L.; Hoogenboom, R. Supramolecular polymer networks: Hydrogels and bulk materials. *Chem. Soc. Rev.* **2016**, *45*, 4013-4031, DOI: 10.1039/C6CS00130K.

4. Goor, O.J.G.M.; Hendrikse, S.I.S.; Dankers, P.Y.W.; Meijer, E.W. From supramolecular polymers to multi-component biomaterials. *Chem. Soc. Rev.* **2017**, *46*, 6621–6637, DOI: 10.1039/C7CS00564D.
5. Kajita, T.; Noro, A.; Matsushita, Y. Design and properties of supramolecular elastomers. *Polymer* **2017**, *128*, 297–310, DOI: 10.1016/j.polymer.2017.03.010.
6. Yan, X.; Wang, F.; Zheng, B.; Huang, F. Stimuli-responsive supramolecular polymeric materials. *Chem. Soc. Rev.* **2012**, *41*, 6042–6065, DOI: 10.1039/C2CS35091B.
7. Herbert, K.M.; Schrettl, S.; Rowan, S.J.; Weder, C. 50th anniversary perspective: Solid-state multistimuli, multiresponsive polymeric materials. *Macromolecules* **2017**, *50*, 8845–8870, DOI: 10.1021/acs.macromol.7b01607.
8. Calvino, C.; Neumann, L.; Weder, C.; Schrettl, S. Approaches to polymeric mechanochromic materials. *J. Polym. Sci. Pol. Chem.* **2017**, *55*, 640–652, DOI: 10.1002/pola.28445.
9. Herbst, F.; Seiffert, S.; Binder, W.H. Dynamic supramolecular poly(isobutylene)s for self-healing materials. *Polym. Chem.* **2012**, *3*, 3084–3092, DOI: 10.1039/C2PY20265D.
10. Roy, N.; Tomović, Ž.; Buhler, E.; Lehn, J.-M. An easily accessible self-healing transparent film based on a 2d supramolecular network of hydrogen-bonding interactions between polymeric chains. *Chem.-Eur. J.* **2016**, *22*, 13513–13520, DOI: 10.1002/chem.201601378.
11. Yang, J.-X.; Long, Y.-Y.; Pan, L.; Men, Y.-F.; Li, Y.-S. Spontaneously healable thermoplastic elastomers achieved through one-pot living ring-opening metathesis copolymerization of well-designed bulky monomers. *ACS Appl. Mater. Interfaces* **2016**, *8*, 12445–12455, DOI: 10.1021/acsami.6b02073.
12. Li, J.; Viveros, J.A.; Wrue, M.H.; Anthamatten, M. Shape-memory effects in polymer networks containing reversibly associating side-groups. *Adv. Mater.* **2007**, *19*, 2851–2855, DOI: 10.1002/adma.200602260.
13. Binder, W.H.; Petraru, L.; Roth, T.; Groh, P.W.; Pálfi, V.; Keki, S.; Ivan, B. Magnetic and temperature-sensitive release gels from supramolecular polymers. *Adv. Funct. Mater.* **2007**, *17*, 1317–1326, DOI: 10.1002/adfm.200601084.
14. Seiffert, S.; Sprakel, J. Physical chemistry of supramolecular polymer networks. *Chem. Soc. Rev.* **2012**, *41*, 909–930, DOI: 10.1039/C1CS15191F.
15. Sijbesma, R.P.; Beijer, F.H.; Brunsveld, L.; Folmer, B.J.B.; Hirschberg, J.H.K.K.; Lange, R.F.M.; Lowe, J.K.L.; Meijer, E.W. Reversible polymers formed from self-complementary monomers using quadruple hydrogen bonding. *Science* **1997**, *278*, 1601, DOI: 10.1126/science.278.5343.1601.
16. Folmer, B.J.B.; Sijbesma, R.P.; Versteegen, R.M.; van der Rijt, J.A.J.; Meijer, E.W. Supramolecular polymer materials: Chain extension of telechelic polymers using a reactive hydrogen-bonding synthon. *Adv. Mater.* **2000**, *12*, 874–878, DOI: 10.1002/1521-4095(200006)12:12<874::AID-ADMA874>3.0.CO;2-C.
17. Sivakova, S.; Bohnsack, D.A.; Mackay, M.E.; Suwanmala, P.; Rowan, S.J. Utilization of a combination of weak hydrogen-bonding interactions and phase segregation to yield highly thermosensitive supramolecular polymers. *J. Am. Chem. Soc.* **2005**, *127*, 18202–18211, DOI: 10.1021/ja055245w.
18. Nair, K.P.; Breedveld, V.; Weck, M. Complementary hydrogen-bonded thermoreversible polymer networks with tunable properties. *Macromolecules* **2008**, *41*, 3429–3438, DOI: 10.1021/ma800279w.
19. Söntjens, S.H.M.; Renken, R.A.E.; van Gemert, G.M.L.; Engels, T.A.P.; Bosman, A.W.; Janssen, H.M.; Govaert, L.E.; Baaijens, F.P.T. Thermoplastic elastomers based on strong and well-defined hydrogen-bonding interactions. *Macromolecules* **2008**, *41*, 5703–5708, DOI: 10.1021/ma800744c.
20. Fawcett, A.S.; Brook, M.A. Thermoplastic silicone elastomers through self-association of pendant coumarin groups. *Macromolecules* **2014**, *47*, 1656–1663, DOI: 10.1021/ma402361z.
21. Tan, C.S.Y.; Agmon, G.; Liu, J.; Hoogland, D.; Janecek, E.-R.; Appel, E.A.; Scherman, O.A. Distinguishing relaxation dynamics in transiently crosslinked polymeric networks. *Polym. Chem.* **2017**, *8*, 5336–5343, DOI: 10.1039/C7PY00574A.
22. Yount, W.C.; Juwarker, H.; Craig, S.L. Orthogonal control of dissociation dynamics relative to thermodynamics in a main-chain reversible polymer. *J. Am. Chem. Soc.* **2003**, *125*, 15302–15303, DOI: 10.1021/ja036709y.
23. Yount, W.C.; Loveless, D.M.; Craig, S.L. Strong means slow: Dynamic contributions to the bulk mechanical properties of supramolecular networks. *Angew. Chem.-Int. Ed.* **2005**, *44*, 2746–2748, DOI: 10.1002/anie.200500026.

24. Yount, W.C.; Loveless, D.M.; Craig, S.L. Small-molecule dynamics and mechanisms underlying the macroscopic mechanical properties of coordinatively cross-linked polymer networks. *J. Am. Chem. Soc.* **2005**, *127*, 14488–14496, DOI: 10.1021/ja054298a.
25. Aboudzadeh, M.A.; Muñoz, M.E.; Santamaría, A.; Fernández-Berridi, M.J.; Irusta, L.; Mecerreyes, D. Synthesis and rheological behavior of supramolecular ionic networks based on citric acid and aliphatic diamines. *Macromolecules* **2012**, *45*, 7599–7606, DOI: 10.1021/ma300966m.
26. Qin, Y.; Jäkle, F. Formation of polymeric Lewis acid–Lewis base complexes with well-defined organoboron polymers. *J. Inorg. Organomet. Polym. Mater.* **2007**, *17*, 149–157, DOI: 10.1007/s10904-006-9084-1.
27. Doshi, A.; Jäkle, F. Polystyrene-supported borane complexes PS-BH₂. *Main Group Chem.* **2006**, *5*, 309–318, DOI: 10.1080/10241220701633705.
28. Cheng, F.; Jäkle, F. Boron-containing polymers as versatile building blocks for functional nanostructured materials. *Polym. Chem.* **2011**, *2*, 2122–2132, DOI: 10.1039/C1PY00123J.
29. Jäkle, F. Recent advances in the synthesis and applications of organoborane polymers. In *Synthesis and application of organoboron compounds*, Fernández, E.; Whiting, A., Eds. Springer International Publishing: Cham, 2015; pp 297–325.
30. Korich, A.L.; Iovine, P.M. Boroxine chemistry and applications: A perspective. *Dalton Trans.* **2010**, *39*, 1423–1431, DOI: 10.1039/B917043J.
31. Qin, Y.; Cui, C.; Jäkle, F. Silylated initiators for the efficient preparation of borane-end-functionalized polymers via atp. *Macromolecules* **2007**, *40*, 1413–1420, DOI: 10.1021/ma061704h.
32. Cheng, F.; Bonder, E. M.; Jäkle, F. *J. Am. Chem. Soc.* **2013**, *135*, 17286–17289, DOI:10.1021/ja409525j.
33. Christinat, N.; Croisier, E.; Scopelliti, R.; Cascella, M.; Röthlisberger, U.; Severin, K. Formation of boronate ester polymers with efficient intrastrand charge-transfer transitions by three-component reactions. *Eur. J. Inorg. Chem.* **2007**, *2007*, 5177–5181, DOI: 10.1002/ejic.200700723.
34. Icli, B.; Solari, E.; Kilbas, B.; Scopelliti, R.; Severin, K. Multicomponent assembly of macrocycles and polymers by coordination of pyridyl ligands to 1,4-bis(benzodioxaborole)benzene. *Chem.-Eur. J.* **2012**, *18*, 14867–14874, DOI: 10.1002/chem.201202313.
35. Luisier, N.; Schenk, K.; Severin, K. A four-component organogel based on orthogonal chemical interactions. *Chem. Commun.* **2014**, *50*, 10233–10236, DOI: 10.1039/C4CC03398A.
36. Luisier, N.; Scopelliti, R.; Severin, K. Supramolecular gels based on boronate esters and imidazolyl donors. *Soft Matter* **2016**, *12*, 588–593, DOI: 10.1039/C5SM02298C.
37. Dodge, L.; Chen, Y.; Brook, M.A. Silicone boronates reversibly crosslink using Lewis acid–Lewis base amine complexes. *Chem.-Eur. J.* **2014**, *20*, 9349–9356, DOI: 10.1002/chem.201402877.
38. Wang, M.; Nudelman, F.; Matthes, R.R.; Shaver, M.P. Frustrated Lewis pair polymers as responsive self-healing gels. *J. Am. Chem. Soc.* **2017**, *139*, 14232–14236, DOI: 10.1021/jacs.7b07725.
39. Marić, M.; Macosko, C.W. Block copolymer compatibilizers for polystyrene/poly(dimethylsiloxane) blends. *J. Polym. Sci. B, Polym. Phys.* **2002**, *40*, 346–357, DOI: 10.1002/polb.10098.
40. Qin, Y.; Cheng, G.; Achara, O.; Parab, K.; Jäkle, F. A new route to organoboron polymers via highly selective polymer modification reactions. *Macromolecules* **2004**, *37*, 7123–7131, DOI: 10.1021/ma035880r.
41. Qin, Y.; Cheng, G.; Sundararaman, A.; Jäkle, F. Well-defined boron-containing polymeric Lewis acids. *J. Am. Chem. Soc.* **2002**, *124*, 12672–12673, DOI: 10.1021/ja020773i.
42. Nose, T. Coexistence curves of polystyrene/ poly(dimethylsiloxane) blends. *Polymer* **1995**, *36*, 2243–2248, DOI: 10.1016/0032-3861(95)95303-I.
43. Chuai, C.; Li, S.; Almdal, K.; Alstrup, J.; Lyngaae-Jørgensen, J. Influence of diblock copolymer on the morphology and properties of polystyrene/poly(dimethylsiloxane) blends. *J. Appl. Polym. Sci.* **2004**, *92*, 2747–2757, DOI: 10.1002/app.20258.
44. Van den Brande, N.; Koning, C.; Geerlings, P.; Van Lier, G.; Van Assche, G.; Van Mele, B. Partially miscible polystyrene/polymethylphenylsiloxane blends for nanocomposites. *J. Therm. Anal. Calorim.* **2011**, *105*, 775, DOI: 10.1007/s10973-011-1473-1.
45. Dvornic, P.R.; Jovanovic, J.D.; Govedarica, M.N. On the critical molecular chain length of polydimethylsiloxane. *J. Appl. Polym. Sci.* **1993**, *49*, 1497–1507, DOI: 10.1002/app.1993.070490901.
46. Kawakami, Y.; Hisada, H.; Yamashita, Y. Polystyrenes with p-oligo-siloxane, silane, germanosiloxane, germane, or stannane as p-substituents as materials for oxygen permeable membranes. *J. Polym. Sci. Pol. Chem.* **1988**, *26*, 1307–1314, DOI: 10.1002/pola.1988.080260505.

47. Lu, S.; Pearce, E.M.; Kwei, T.K. Novel silanol-containing polymers and their blends. *Polym. Prepr. (Am. Chem. Soc., Div. Polym. Chem.)* **1998**, *39*, 560-561.
48. Lindsley, C.W.; Hodges, J.C.; Filzen, G.F.; Watson, B.M.; Geyer, A.G. Rasta silanes: New silyl resins with novel macromolecular architecture via living free radical polymerization. *J. Comb. Chem.* **2000**, *2*, 550-559, DOI: 10.1021/cc000037f.
49. Rossi, R.; Carpita, A.; Ciofalo, M.; Lippolis, V. Selective and efficient syntheses of phototoxic 2,2':5',2''-terthiophene derivatives bearing a functional substituent in the 3'- or the 5-position. *Tetrahedron* **1991**, *47*, 8443-8460, DOI: 10.1016/S0040-4020(01)96185-X.
50. Bauer, L.; Gardella, L.A. Addition of thiourea to 2- and 4-vinylpyridines. *J. Org. Chem.* **1961**, *26*, 82-85, DOI: 10.1021/jo01060a019.



© 2018 by the authors. Submitted for possible open access publication under the terms and conditions of the Creative Commons Attribution (CC BY) license (<http://creativecommons.org/licenses/by/4.0/>).