

Parametric experimentation on pantographic unit cells reveals local extremum configuration

N. Nejadsadeghi · M. De Angelo · R. Drobnicki · T. Lekszycki · F. dell'Isola · A. Misra

Received: date / Accepted: date

Abstract Pantographic metamaterials are known for their ability to have large deformation while remaining in the elastic regime. We have performed a set of experiments on 3D printed pantographic unit cells to parametrically

N. Nejadsadeghi
Mechanical Engineering Department, University of Kansas, 1530 W. 15th Street, Learned Hall, Lawrence, KS 66045-7609, USA
E-mail: nima.nejadsadeghi@ku.edu

M. De Angelo
Dipartimento di Ingegneria Civile, Edile-Architettura e Ambientale, Università degli Studi dell'Aquila, Via Giovanni Gronchi 18 - Zona industriale di Pile, 67100 L'Aquila, Italy
Civil, Environmental and Architectural Engineering Department, The University of Kansas, 1530 W. 15th Street, Lawrence, KS 66045-7609, USA

R. Drobnicki
Dipartimento di Ingegneria e Scienze dell'Informazione e Matematica Università degli Studi dell'Aquila, L'Aquila, Italy

T. Lekszycki
Institute of Mechanics and Printing, Warsaw University of Technology, 85 Narbutta Street, 02-524 Warsaw, Poland
Department of Experimental Physiology and Pathophysiology, Medical University of Warsaw, 1b Banacha Street, 02-097 Warsaw, Poland

F. dell'Isola
Dipartimento di Ingegneria Strutturale e Geotecnica, Università degli Studi di Roma "La Sapienza.", Via Eudossiana 18, 00184 Rome, Italy
International Research Center M&MoCS, Università degli Studi dell'Aquila, Via Giovanni Gronchi 18 - Zona industriale di Pile, 67100 L'Aquila, Italy

A. Misra
Civil, Environmental and Architectural Engineering Department, The University of Kansas, 1530 W. 15th Street, Lawrence, KS 66045-7609, USA

investigate their response when undergoing tensile, compression, and shear loading with the aim of i) studying the role of each parameter in the resultant mechanical behavior of the sample, and ii) providing a benchmark for the mathematical models developed to describe pantographic structures. Results show the existence of local extrema in the space of the geometrical parameters, suggesting the use of optimization techniques to find optimal geometrical parameters resulting in desired functionalities. We have also performed tensile relaxation tests on the samples, with the results indicating the complexity of the dynamic behavior and the existence of multiple relaxation characteristic times. Such results can be used to for calibrating mathematical models describing pantographic structures under dynamic loadings.

Keywords Pantographic metamaterials · Parametric investigation · Additive manufacturing · Complex structures · Experimental tests

1 Introduction

Since the advent and continuous progress of additive manufacturing techniques, new horizons in terms of analysis of the mechanical behavior of materials and design of new materials have been opened. By employing the most advanced processes it is now possible to create objects with complex geometries at very small length scale. Arranging such complex objects in a periodic pattern, playing the role of micro- or nano- scale building block, results in micro-structured materials, also called *metamaterials*, whose macroscopic mechanical behavior is strongly dependent on the characteristics of the kinematic field of the given micro-structure.[1,2] This influences the research in the field of innovative materials as we are now able to endow them with a micro-structure, which is potentially customizable and tunable according to the applications to be addressed. However, the new promising possibilities require the definition of more refined mathematical models, involving detailed kinematic fields and higher order gradient terms in their equations of motion to capture their unusual behavior. Examples are represented by pantographic structures [3–7], for which their exotic behavior has to be described with higher gradient continuum theories [8–10] or micromorphic theories [11,12], granular media [13–19], auxetic material [20,21] and functionally graded material [22, 23].

Pantographic structures have recently been investigated particularly from a theoretical, mechanical and manufacturing point of view because of their peculiar capability to undergo large tensile deformation while remaining in elastic regime [3]. The design of such *metamaterial* comes from a mathematical understanding of the related mechanical problem and considerations on the insufficiency of classical theories to describe materials with complex micro-structure, and it has been conceived so that its deformation energy depends on the second gradient of the displacement [7,24–26]. Morphologically, the pantographic system can be described as a double array of mutually orthogo-

nal beams, also called fibers, interconnected by elastic cylinders at intersection points, called pivots [27].

Earlier investigations can be found in a series of papers (see e.g. [5, 27–31]) in which the authors address the problem of determining the mechanical properties of pantographic *metamaterials*. Various mathematical models have also been proposed which can be classified into two-types i) discrete, as in [27, 29, 32–36], wherein a finite set of rotational and extensional springs are introduced to describe the complex deformation phenomenon occurring in the micro-structure; or ii) continuous, as in [27, 33, 37, 38], which can be further distinguished into purely continuous ones, wherein a generalized plate model is used (of the same kind of those proposed e.g. in [11, 12], and into hybrid discrete/continuous ones, wherein beams (i.e. 1D continua) form lattices by means of interconnecting pivots placed at finite distances (see [39–42])). The main motivation of these works is to find a reasonable compromise between predictive capacity and computational feasibility in analyzing pantographic structures. Both continuous and discrete models demonstrate their own peculiarities in facing the problem and some comparisons have been recently presented where the validation of the models is demonstrated by using experimental results [29, 43, 44]. It is noteworthy that the behavior observed during tensile test [36, 44, 45], shear test [45–47] and also torsion test [45] conducted on specimens of pantographic structures (as the kind described in [27]) is well represented by the aforementioned models. However it is not clear how the geometric features of the pantographic micro-structure affect the mechanical behavior of the specimens tested yet. An understanding of the role of geometrical parameters on the macroscopic behavior of pantographic structures seems indispensable for the purpose of designing of such structures with desired functionalities. Indeed, regardless of the nature of the approach (continuous or discrete) used to forecast the behavior of the system under various load and boundary conditions, it is necessary to estimate the relevant constitutive parameters on which the deformation energy function depends. Also, an investigation on pantographic beam structures with relatively small number of cells could be, according to the theory developed in [48], useful to determine information about the extent to which continuum modeling can approximate more spatially extended structures. We believe that better identification schemes have to be devised for the aim of identifying the mechanical properties and achieving structural optimizations. Such identification schemes require experimental results sufficient for calibrating mathematical models.

In this paper we present a series of results obtained from a set of experimental tests performed on specimens of pantographic structure. Rather than using larger samples, the specimens considered herein can be defined as the elementary module of the pantographic micro-structure. Tensile, compression, shear and tensile relaxation tests are performed on a large set of polyamide specimens whose geometric features are presented in Section 2. In the same section we present the prescriptions of the tests and the tools employed. Section 3 is devoted to the results and corresponding discussions of the experimental data.

In the conclusion section an outline about the results is given with considerations regarding future studies.

2 Fabrication and experimental setup

The specimens considered herein represent the unit cell of the micro-structure employed to build a larger pantographic structure. The geometry of the objects was initially generated employing the CAD software SolidWorks (Dassault System SolidWorks Corporation, Waltham, MA, USA). The specimens were thereafter printed using 3D printer Formiga P 100 (EOS GmbH, Munich, Germany) at the University of Technology, Warsaw, Poland. The 3D printer uses a selective laser sintering (SLS) technology to produce the pantographic structure out of polyamide powder (PA2200), where the average grain size of the powder used was $56\mu\text{m}$. The complete set of specimen contains thirty three objects characterized by different values of the geometric parameters (see **Fig. 1**). In order to easily refer to each specimen, depending on the value assumed by the parameter p , we arrange the specimens with $p = 5\text{ mm}$ in a group A and the specimens with $p = 8\text{ mm}$ in a group B. Furthermore, an index $i = 1, 2, 3, 4$ is assigned to each specimen depending on the length of the pivot, which indicates sample type. Details about the sample type, number and geometric features can be found in **Table 2**. For each sample type a tensile, compression, tensile relaxation and a shear test were performed. A *Bose ElectroForce 3200* testing-device controlled by the software WinTest Material Testing System was used to perform all the experiments presented in the following. The load cell used to measure the reaction force values has a measurement range of $\pm 22\text{ N}$, a measurement uncertainty of 0.1% and precision of 0.001 N. All the tests were performed in displacement control, which is measured with the built-in transducer with the range of $\pm 6.5\text{ mm}$, a measurement uncertainty of 0.1% and precision of 0.001 mm. For evaluations on the deformation fields by means of digital image correlation technique (DIC), pictures were taken during the tensile, compression and shear tests. DIC along with relevant discussions on the deformation field, similar to [35], will be pursued in a separate paper in the future. To this end the specimens were sprayed on their surface with a black spray -to make a speckle pattern- prior to the testing, and a NIKON D300 digital camera was used to take consecutive pictures at fixed time intervals with image resolution of 4288 by 2848 pixels. The tensile test is experimentally carried out by keeping fixed one side of the specimen and applying an axial displacement on the other side. For this test, the imposed values of displacement are 4 mm and 6 mm, for groups A and B respectively, at the rate of 0.1 mm/s. A similar setup has been used to conduct the compression test but in this case, obviously, the imposed displacement has opposite sign. The compression displacements applied to the specimens of group A and group B are of 10 mm and 12 mm respectively, at a rate of 0.1 mm/s. The experimental realization of the shear test is carried out by fixing the specimen on one side while on the other side a tangential displacement is applied. The displacement occurs in the plane on which the specimen lies. The specimens of both groups A and B are displaced up to 10 mm at the rate of 0.1 mm/s. The tensile relaxation test, whose setup is similar to that of the tensile test, prescribes the application of three successive load levels, starting from 2 mm

Table 1 Constant parameters shared by all the specimens.

a (mm)	b (mm)	d (mm)	L (mm)	θ (rad)	ϕ (rad)
1.2	1	1	5	$\frac{\pi}{2}$	$\frac{\pi}{4}$

for group A and from 4 mm for group B, being the increase of displacement of each load step equal to 1 mm. Every load level is maintained constant for eight hours. This duration has been selected after a previously conducted test on a specimen for two days which showed a great portion of relaxation occurs in the first eight hours. One has to remark that the fulfillment of all the devised experiments required to design and 3D print some support structures (see **Fig. 2**) in order to hold the specimens during the tests. For the tensile, compression and tensile relaxation test, two clamps have been printed employing a Mojo 3D printer (FDM Fused Deposition Modeling, by Stratasys) using as constituent material an acrylonitrile butadiene styrene (ABS) thermoplastic (**Fig. 2(a)**). Similarly, for the shear test a rigid support structure and two different clamps have been created by employing the same 3D printer and constituent material. The measurement error introduced by the deformability of these support objects was considered negligible following some numerical simulations of the experiments in FE software ABAQUS.

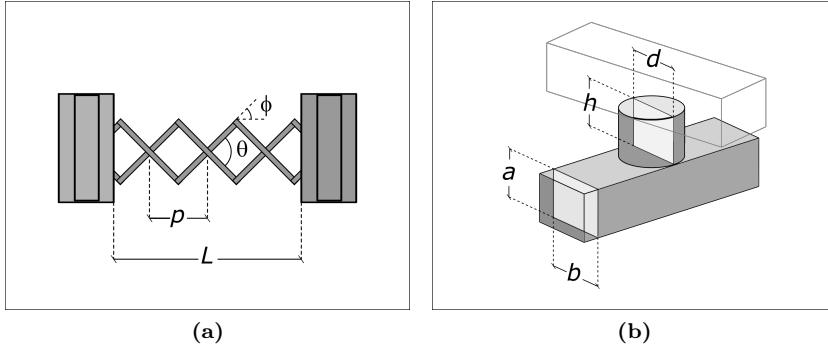
**Fig 1** Parameters describing the pantographic structure.

Table 2 Type of specimen, number and values of the distinctive parameters for each type of specimen.

Specimen type	number of specimens	p (mm)	h (mm)
A1	4	5	1
A2	3	5	1.5
A3	4	5	2
A4	4	5	3
B1	5	8	1
B2	4	8	1.5
B3	5	8	2
B4	4	8	3

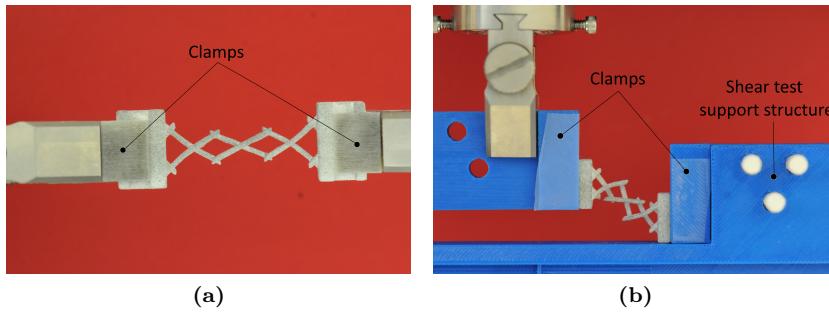


Fig 2 Experimental setup of the tests for (a) tensile, compression and tensile relaxation tests (b) shear test.

3 Results and discussion

The results presented here comprise a complete set of tests sufficient to calibrate pantographic models, and therefore can be used as benchmarks for the developed theoretical models. In the following, we briefly comment the peculiarities observed. Note that in the following we will use the term stiffness to refer to the trend of the values generally assumed by the ratio between force and imposed displacement, but no specific force-displacement relation is meant.

In **Fig. 3** the results of the tensile test for the two groups of specimens are shown. In the plots related to group A in **Fig. 3(a)** one can notice that the stiffness of the sample is inversely proportional to length of the pivots. Indeed for a given value of displacement, among those considered in the experiments, the force decreases progressively from the maximum value, measured for the sample A1, to the minimum value, measured for the sample A4. Furthermore, observing singularly the data for each specimen, the curves related to A2, A3 and A4 have almost a linear behavior while for the specimen A1 a hardening tract arises after 2 mm of displacement. This could be attributed to the plastic

deformation of the pivots or increased axial extension of the central beams for the specimen A1. In **Fig. 3(b)** the plots for the tensile test related to the specimen of the group B are shown. Also in this case the data depicts an overall inverse proportionality between the stiffness and the length of the pivots, but for the specimen B1 the behavior is different. The reaction force values decrease gradually from B2 to B4 but the curve of B1 overlaps the plot of B4 for the most part and it has a hardening part starting from about 4 mm of elongation. With a more detailed look at the data, the specimens B3 and B4 seem to have linear behaviors while for the specimens B1 and B2 an incipient hardening behavior can be seen for higher values of displacement. The plots

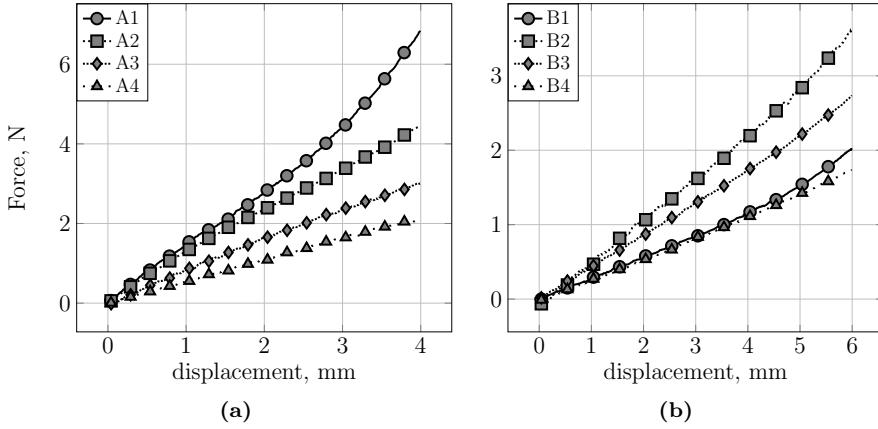


Fig 3 Plots of the data from experimental tensile test for **(a)** group A **(b)** group B.

in **Fig. 4** give information about the force trend depending on the length of the pivots, for the tensile test. Specifically, in each plot the abscissa axis reports the sample type while the ordinate axis reports the measured force, which is evaluated for four different values of imposed displacements. In **Fig. 4(a)**, which shows the data related to the group A, it can be observed that for a given applied displacement, the force exerted is decreasing with the length of the pivot, which represents the inverse proportionality mentioned above. On the contrary, the specimens of group B do not follow the aforementioned inverse proportionality. Indeed, in **Fig. 4(b)**, it is noticeable that there is a maximum force value corresponding to the specimen B2. This aberration deserves mathematical justification and will be further investigated in future works.

In **Fig. 5** the experimental data of the compression tests are plotted for both group A and group B. In **Fig. 5(a)**, which shows the data regarding the group A, it is hard to recognize a linear stage as the behavior seems to be nonlinear even for small values of the imposed displacement. Up to 6 mm of

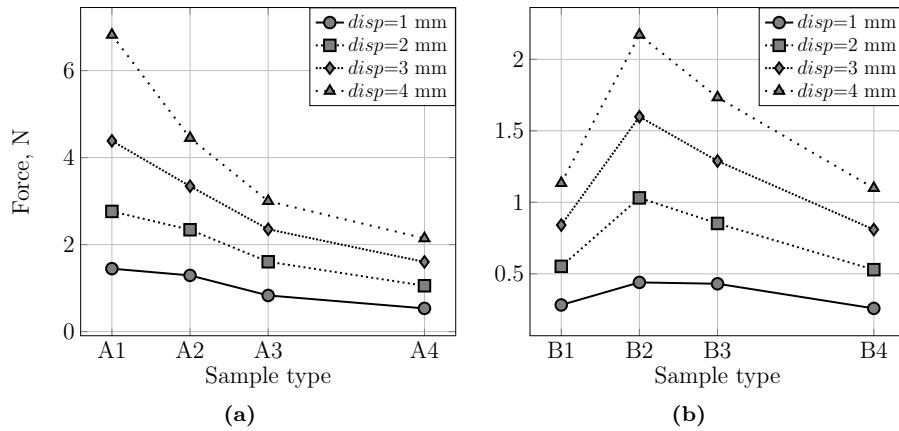


Fig 4 Interpolation of the force values with respect to the length of the pivots in tensile tests. Each line refers to a specific value of the imposed displacement ("*disp*" in the legend) for (a) group A (b) group B.

compression, all the curves, whose values are close to each other, describe a softening behavior. After 6 mm of compression, the behavior of the samples changes and reaction forces increase rapidly, describing a hardening behavior. An interpretation of this observation is attempted in the following with the help of the pictures taken during the test. We can remark that the group A observes the inverse proportionality relation between the stiffness of the sample and the length of the pivots. Similar considerations can be made looking at **Fig. 5(b)**. Indeed, the plots of the compression test for group B describe a softening behavior with a not easily recognizable initial linear stage and a hardening behavior starting from about 10 mm of displacement. Similar to the results of tensile test, the sample B2 leads to the highest values of reaction force. We remark that the curve related to sample B1 is closer to the values assumed by sample B4 up to 10 mm of compression while starts to rise fast over this value, overlapping the plot of sample B2 for higher value of compression. The higher stiffness of sample B2 can be observed in the **Fig. 6(b)**, where the force values recorded at several displacement values are plotted with respect to the length of the pivots. It can be noted that in correspondence of sample B2 the plots have a maximum. In **Fig. 6(a)**, a similar plot is shown for group A which for every displacement level observes the inverse proportionality between stiffness and length of the pivots.

The data related to the shear test are plotted in **Fig. 7**. The shear stiffness is inversely proportional to the length of the pivots for both the groups A and B, but also in this case the sample B1 behaves differently. In **Fig. 7(b)**, it can be noted that the plot of the data for the shear test regarding the sample B1 is between the plots of samples B2 and B3. Considering separately the two groups, in **Fig. 7(a)** the behavior of all the samples belonging to group A is

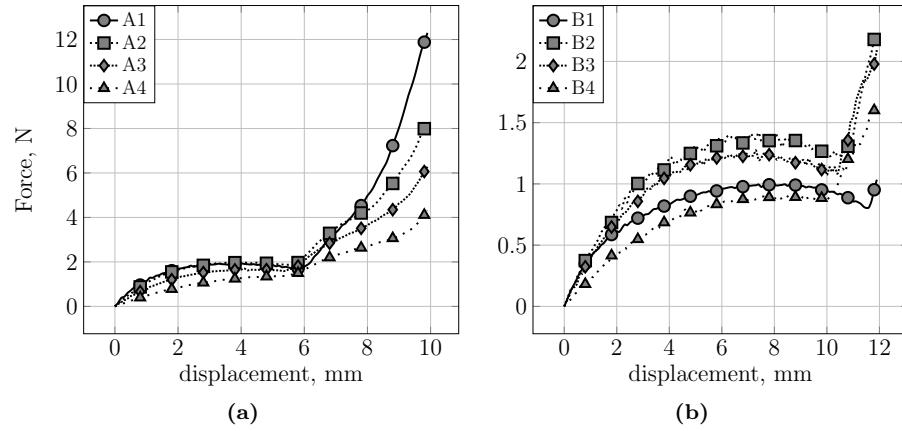


Fig 5 Plots of the data from experimental compression test for (a) group A (b) group B.

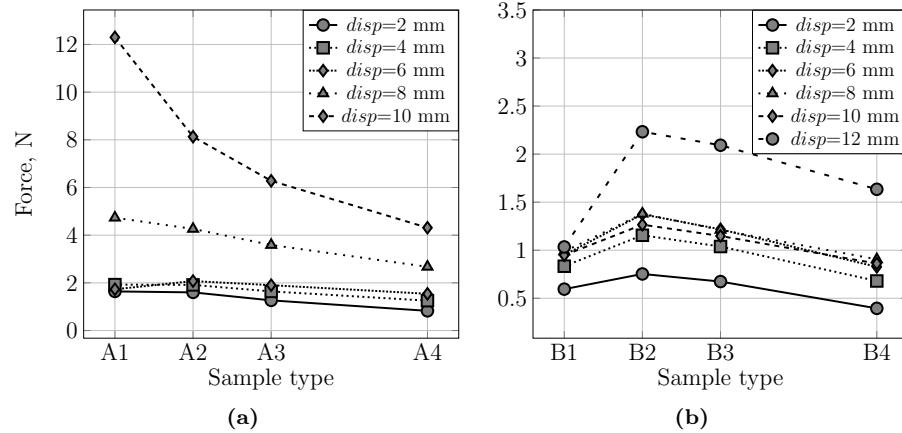


Fig 6 Interpolation of the force values with respect to the length of the pivots in compression tests. Each line refers to a specific value of the imposed displacement ("disp" in the legend) for (a) group A (b) group B.

linear for the most part and has an incipient hardening part for higher values of the imposed displacement, more evident for the sample A1. The plots of the group B reported in **Fig. 7(b)** show that all the samples have linear behavior within the entire range of displacement. It is anticipated that for a larger displacement, group B also shows a nonlinear hardening effect. The plots in **Fig. 8** give information about the stiffness trend of the samples varying the length of the pivots, for both group A and B. The existence of local extrema in the space of the geometrical parameters can be noted for sample type B1.

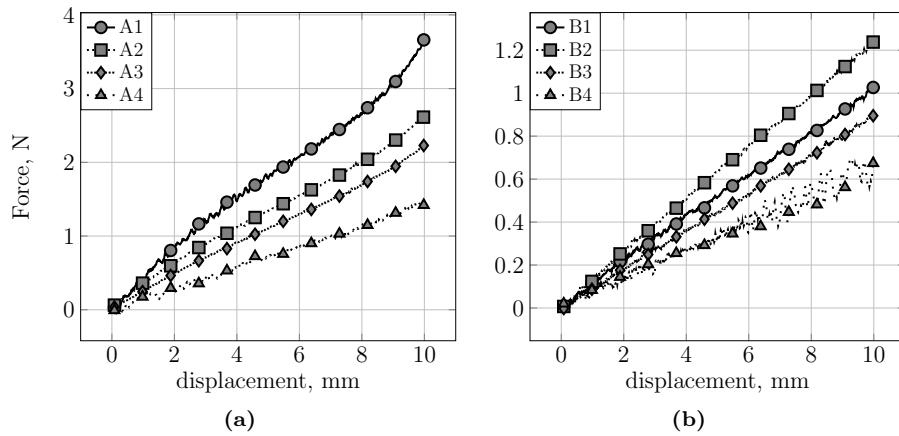


Fig 7 Plots of the data from experimental shear test for (a) group A (b) group B.

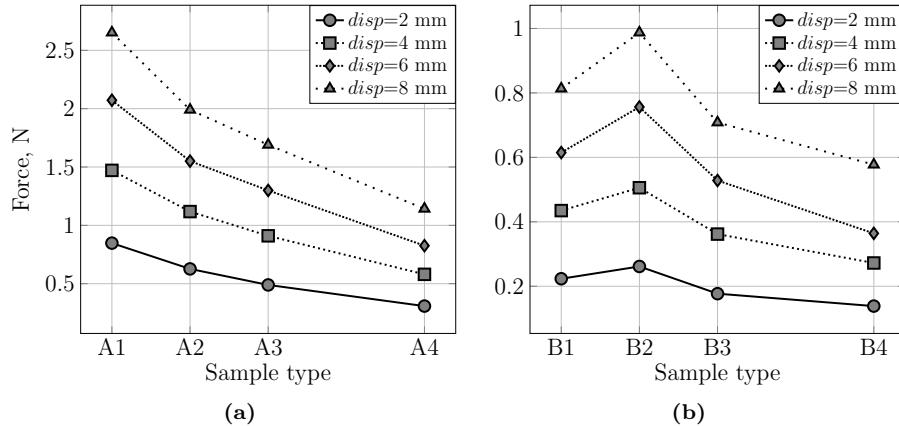


Fig 8 Interpolation of the force values with respect to the length of the pivots in shear tests. Each line refers to a specific value of the imposed displacement ("disp" in the legend) for (a) group A (b) group B.

Comparisons between the tensile, compression and shear tests are shown in **Fig. 9** for all the specimens. It can be noted that, in all the graphs of **Fig. 9**, the highest stiffness is observed during the tensile test, the lowest during the shear test and intermediate values during the compression test.

In order to give an interpretation of the behavior of each pantographic structure undergoing tensile, compression and shear tests, we plot in **Fig. 10** the tensile, compression and shear tests related to the sample A1. The numeric marks from 1 to 5 plotted in **Fig. 10** are related to the corresponding

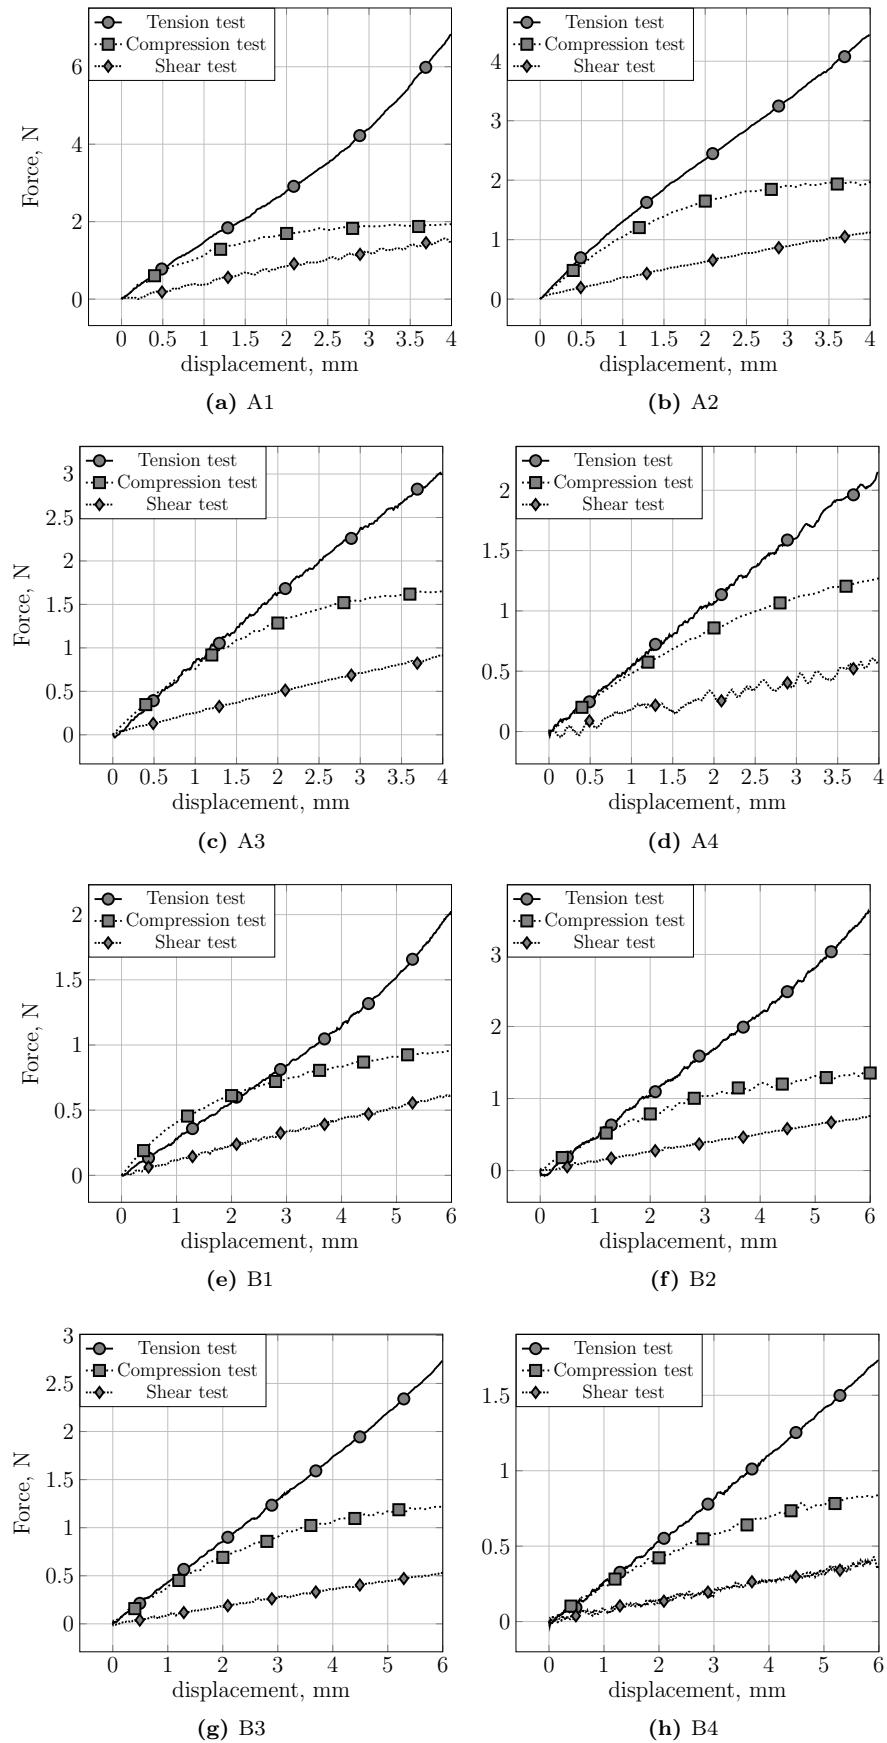


Fig 9 Comparison of the experimental data of all the samples between tensile test, compression test and shear test.

picture number in **Fig. 11** for each test, respectively. The pictures in **Fig. 11** visualize the equilibrium shape for the considered state of the sample in the force-displacement plots. A main observation emerges by looking at **Fig. 10(a)** and at the corresponding line in **Fig. 11**. Hardening behavior can be observed for the two cases of shear and tension. For the compression test, however, a softening behavior is observable. The hardening behavior noticed between steps 4 and 5 in the compression test **Fig. 11(b)** is due to natural contact between the constituting beams of the pantographic micro-structure, and is merely plotted for completeness. Another interesting remark is that in all three different tests reported in **Fig. 11**, the central beams of each specimen experience indiscernible bending deformation and, primarily, undergo rigid body motion. As is observed in [27], major part of the bending and torsional energies are therefore stored in beams closer to the boundaries and pivots in central regions of the structure, respectively.

The data related to the tensile relaxation test are shown in **Fig. 12** for both group A and group B. We recall from Section 1 that the test prescribes three displacement steps, starting from 2 mm to 4 mm for group A, and starting from 4 mm to 6 mm for group B, with a displacement increment of 1 mm applied at the rate of 0.1 mm/s. Every load is maintained constant for eight hours. In **Fig. 12**, reaction force versus time is plotted for each of the specimen tested. There is a good agreement between the specimens tested from group A in **Fig. 12(a)** and their counterparts for the tensile test in **Fig. 3(a)**. However, for the group B, the plot for the specimens B1 in **Fig. 12(b)** lies closer to the one plotted for the specimen B3 rather than B4, which is different from the same geometry behavior reported above in **Fig. 3(b)**. This observation may be attributed to the inevitable existence of fabrication defects, which makes different samples with the same geometry different in behavior.

The stress versus time data of sample A1 has been fitted using a Prony series. The Generalized Maxwell model, also known as the Wiechert model (it takes into account that the relaxation does not occur at a single time, but at a distribution of times), has been considered to model the linear viscoelasticity, which is assumed to be valid. In order to validate this assumption the tensile relaxation module E , which is the ratio between the force and the constant applied displacement, versus time is plotted in **Fig. 13(a)** for the three load steps considered in the experiment. The observed overlapping of the three plots verifies the linear viscoelasticity assumption. In **Fig. 13(b)** the comparison between the experimental data and the Prony series $F(t)$ coming from the fitting procedure is shown. The function $F(t)$ defines the relation between force and the time and has the following general form

$$F(t) = F_0 + \sum_{n=1}^N F_n e^{-\frac{t}{\tau_n}} \quad (1)$$

where F_0 is the force when the specimen is completely relax, τ_n is the characteristic relaxation time, and F_n is the force exerted by the n -th brace of the model. We report in **Table 3** the values of the parameters identified for each

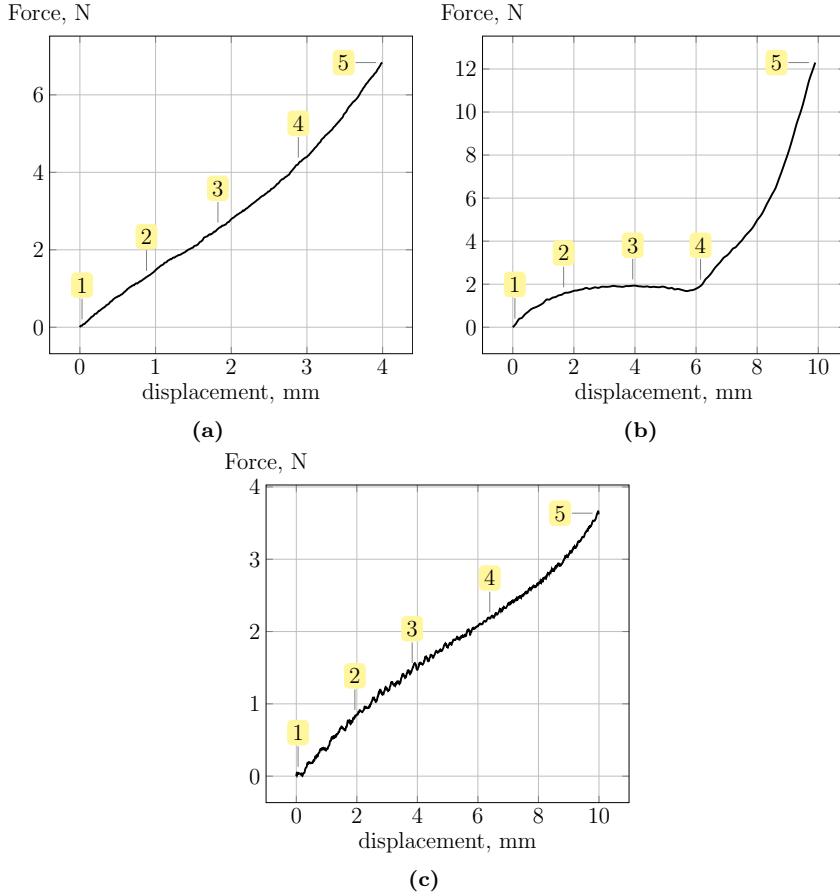


Fig 10 (a) Tensile (b) compression and (c) shear plots of force versus displacement for the sample A1.

Prony series terms for the specimen A1, along with the other specimen types for all the three steps of loading. Note that for the steps two and three of the loading, a shift in time has been done such that the start of the step coincides with zero time. The identified parameters in Tab. 3 have been computed using a least square approach, and the minimum values for the third and fourth characteristic times were chosen to be 0.001 and 0.0001 seconds, respectively. Smaller values for the second and third characteristic times changed the results only negligibly. An analysis on the effect of characteristic times less than 0.01 reveals their major effect only in the first few seconds of the relaxation. However, the existence of the third and fourth terms proved necessary to properly model the small time range behavior. A requisite for additional terms in the Prony series have also been reported in [49]. We note that the assumption of linear viscoelasticity is violated for the application of larger displacements

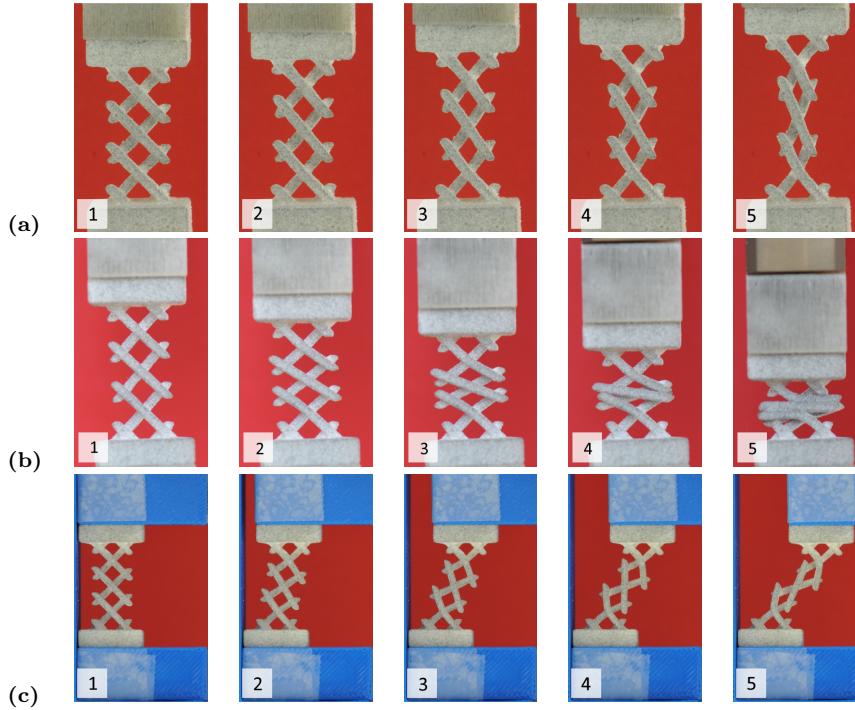


Fig 11 Pictures displaying the deformation of sample A1 under tensile, compression and shear test at five different stages.

where geometrical nonlinearities of the structure, damage, and plastic deformation in the unit cell become significant.

4 Conclusions

In the presented work, we conducted a complete series of tensile, shear, compression and tensile relaxation experiments on a set of specimens of pantographic structures. The specimens differed in two geometrical characteristics, allowing us to parametrically investigate each of the varied geometrical parameters effect on the resultant behavior of the structure. While the samples in group A were behaving in an expected fashion where smaller pivot length results in larger reaction force, group B showed an aberration. To describe the structure's behavior completely, therefore, we will need refined mathematical models. The data presented here shows the behavior of a unit cell of a larger pantographic structure [27], and therefore can be used to calibrate mathematical models. The solidness of such models can be tested by examining whether unusual behavior (such as what we observed for the sample type B2) can be resulted from the model. As geometrical parameters can be changed to cause different behavior in the pantographic structures, the accepted model can then

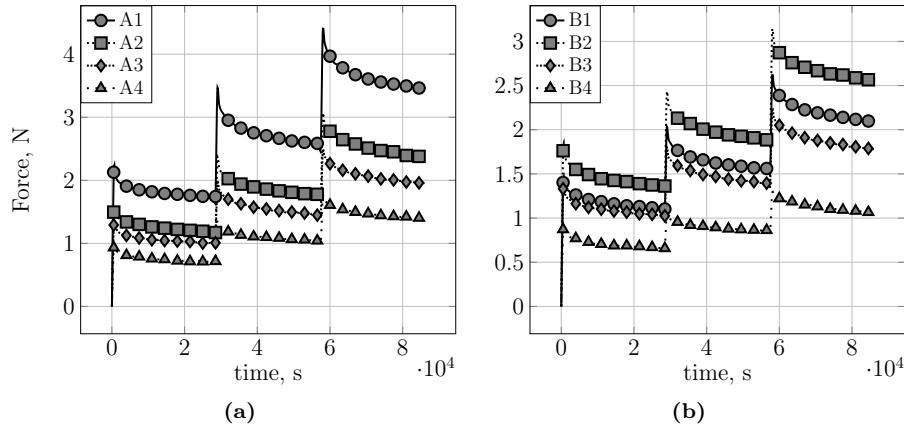


Fig. 12 Plots of the data from experimental tensile relaxation test for (a) group A (b) group B.

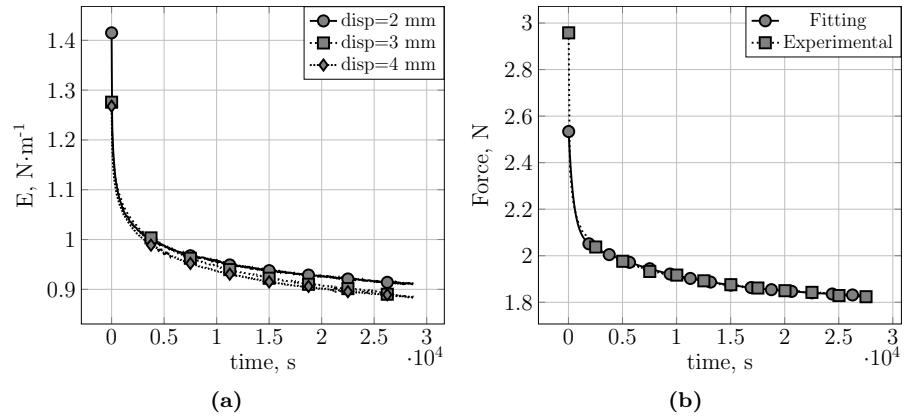


Fig. 13 (a) Tensile relaxation modulus for the three steps of relaxation test on specimen A1. **(b)** Experimental and fitted relaxation behavior of the specimen A1.

be utilized to find optimal geometrical parameters pertaining to a desired behavior using optimization algorithms.

The set of conducted tests comprise a procedure to characterize pantographic structures and can be used to test similar pantographic structures with different constitutive materials. This allows a comparison to account for the constitutive materials of the structure, and will be beneficial, especially in mathematical modeling of pantographic structures undergoing dynamic loading. To this end, fatigue test along with investigation of the micro-structure of the constituent, both before and after the rupture of the structure, will be

Table 3 Tensile relaxation Prony series terms for sample A1 for 2 mm displacement.

Type	Step	F_0 (N)	F_1 (N)	F_2 (N)	F_3 (N)	F_4 (N)	τ_1 (sec)	τ_2 (sec)	τ_3 (sec)	τ_4 (sec)
A1	1 st	1.826	0.2479	0.4500	0.2031	0.2308	10000	500.0	0.0010	0.0001
A1	2 nd	2.633	0.5335	0.4712	0.2186	0.2186	10720	627.0	0.0010	0.0001
A1	3 rd	3.537	0.6679	0.5842	0.2810	0.2810	8581	492.0	0.0010	0.0001
A2	1 st	1.249	0.2723	0.2718	0.0775	0.1465	7882	256.9	0.0010	0.0001
A2	2 nd	1.828	0.3663	0.3154	0.1016	0.1211	9712	566.5	0.0010	0.0001
A2	3 rd	2.427	0.5163	0.4001	0.1551	0.1622	9895	446.1	0.0010	0.0001
A3	1 st	1.038	0.2039	0.2682	0.0786	0.1473	8816	530.7	0.0010	0.0001
A3	2 nd	1.486	0.3636	0.2432	0.0667	0.0662	9271	528.1	0.0010	0.0001
A3	3 rd	1.997	0.3969	0.3057	0.0977	0.0970	8821	500.3	0.0010	0.0001
A4	1 st	0.7159	0.1831	0.1731	0.0597	0.0593	9222	434.5	0.0010	0.0001
A4	2 nd	1.0524	0.2116	0.2000	0.0122	0.0130	9724	323.0	0.0010	0.0001
A4	3 rd	1.417	0.2623	0.1777	0.0568	0.0562	9086	486.4	0.0010	0.0001
B1	1 st	1.113	0.2555	0.3151	0.0804	0.0806	8425	235.1	0.0010	0.0001
B1	2 nd	1.549	0.3025	0.2354	0.1014	0.1010	9924	522.5	0.0010	0.0001
B1	3 rd	2.101	0.3733	0.3114	0.1458	0.1453	8847	444.1	0.0010	0.0001
B2	1 st	1.411	0.3119	0.3696	0.1562	0.1566	7598	344.8	0.0010	0.0001
B2	2 nd	1.925	0.3534	0.2498	0.0890	0.0885	9064	457.8	0.0010	0.0001
B2	3 rd	2.593	0.3845	0.3436	0.1338	0.1448	9792	573.2	0.0010	0.0001
B3	1 st	1.046	0.2149	0.2905	0.1180	0.1170	8779	426.9	0.0010	0.0001
B3	2 nd	1.405	0.2795	0.1602	0.0534	0.0530	9676	485.2	0.0010	0.0001
B3	3 rd	1.787	0.3443	0.2147	0.0787	0.0789	10150	520.7	0.0010	0.0001
B4	1 st	0.6518	0.1715	0.1566	0.0508	0.0511	942.1	471.0	0.0010	0.0001
B4	2 nd	0.8584	0.1396	0.0713	0.0223	0.0223	887.4	398.3	0.0010	0.0001
B4	3 rd	1.069	0.2029	0.0934	0.0238	0.0233	964.0	221.7	0.0010	0.0001

studied in future work, which should also take into account material models with the presence of a damage potential as considered in [50–54], because of the greater deformations the pivots undergo. Indeed, we believe that the first natural continuation of our survey in the field of pantographic metamaterial is to introduce the elasto-plastic behavior of the constituent material, at least for the pivots. Useful information about their optimal shape could be obtained following the method described in [55–58].

A further investigation, which can also lead to interesting engineering applications, is represented by the modeling of pantographic structures, even at the scale described in this article, immersed in a soft matrix. This type of study can be conducted by means of the definition of appropriate tensors of Eshelby or Green. Some useful results for this purpose are reported in [10, 59–63]. Finally, it would be interesting to study the dynamics in pantographic structures of the same dimensions as those presented in this article. In fact, the propagation of waves in generalized continua [64–66] is a non-trivial problem and can lead to unexpected results. Some preliminary results in the field of pantographic structures can be found in [67, 68].

Acknowledgements This research is supported in part by the United States National Science Foundation grant CMMI -1727433.

References

1. Barchiesi, E., Spagnuolo, M., Placidi, L.: Mechanical metamaterials: a state of the art. *Mathematics and Mechanics of Solids* **24**(1), 212–234 (2019)
2. Placidi, L., Rosi, G., Barchiesi, E.: Analytical solutions of 2-dimensional second gradient linear elasticity for continua with cubic-d 4 microstructure. In: *New Achievements in Continuum Mechanics and Thermodynamics*, pp. 383–401. Springer (2019)
3. dell'Isola, F., Seppecher, P., Alibert, J.J., Lekszycki, T., Grygoruk, R., Pawlikowski, M., Steigmann, D., Giorgio, I., Andreaus, U., Turco, E., et al.: Pantographic metamaterials: an example of mathematically driven design and of its technological challenges. *Continuum Mechanics and Thermodynamics* pp. 1–34 (2018)
4. Misra, A., Lekszycki, T., Giorgio, I., Ganzosch, G., Müller, W.H., dell'Isola, F.: Pantographic metamaterials show atypical poynting effect reversal. *Mechanics Research Communications* **89**, 6–10 (2018)
5. dell'Isola, F., Lekszycki, T., Pawlikowski, M., Grygoruk, R., Greco, L.: Designing a light fabric metamaterial being highly macroscopically tough under directional extension: first experimental evidence. *Zeitschrift für angewandte Mathematik und Physik* **66**, 3473–3498 (2015)
6. Placidi, L., Barchiesi, E., Turco, E., Rizzi, N.L.: A review on 2d models for the description of pantographic fabrics. *Zeitschrift für angewandte Mathematik und Physik* **67**(5), 121 (2016)
7. Barchiesi, E., Placidi, L.: A review on models for the 3d statics and 2d dynamics of pantographic fabrics. In: *Wave Dynamics and Composite Mechanics for Microstructured Materials and Metamaterials*, pp. 239–258. Springer (2017)
8. Auffray, N., dell'Isola, F., Eremeyev, V., Madeo, A., Rosi, G.: Analytical continuum mechanics à la Hamilton–Piola least action principle for second gradient continua and capillary fluids. *Mathematics and Mechanics of Solids* **20**(4), 375–417 (2015)
9. Spagnuolo, M., Andreaus, U.: A targeted review on large deformations of planar elastic beams: extensibility, distributed loads, buckling and post-buckling. *Mathematics and Mechanics of Solids* **24**(1), 258–280 (2019)
10. Franciosi, P., Spagnuolo, M., Salman, O.U.: Mean green operators of deformable fiber networks embedded in a compliant matrix and property estimates. *Continuum Mechanics and Thermodynamics* pp. 1–32 (2018)
11. Pietraszkiewicz, W., Eremeyev, V.: On natural strain measures of the non-linear micropolar continuum. *International Journal of Solids and Structures* **46**(3), 774–787 (2009)
12. Altenbach, H., Eremeyev, V.: On the linear theory of micropolar plates. *ZAMM-Journal of Applied Mathematics and Mechanics/Zeitschrift für Angewandte Mathematik und Mechanik* **89**(4), 242–256 (2009)
13. Misra, A., Poorsolhjouy, P.: Granular micromechanics model for damage and plasticity of cementitious materials based upon thermomechanics. *Mathematics and Mechanics of Solids* p. 1081286515576821 (2015)
14. Misra, A., Singh, V.: Thermomechanics-based nonlinear rate-dependent coupled damage-plasticity granular micromechanics model. *Continuum Mechanics and Thermodynamics* **27**(4–5), 787 (2015)
15. Yang, Y., Misra, A.: Micromechanics based second gradient continuum theory for shear band modeling in cohesive granular materials following damage elasticity. *International Journal of Solids and Structures* **49**(18), 2500–2514 (2012)
16. Misra, A., Poorsolhjouy, P.: Grain-and macro-scale kinematics for granular micromechanics based small deformation micromorphic continuum model. *Mechanics Research Communications* **81**, 1–6 (2017)
17. Misra, A., Poorsolhjouy, P.: Identification of higher-order elastic constants for grain assemblies based upon granular micromechanics. *Mathematics and Mechanics of Complex Systems* **3**(3), 285–308 (2015)

18. Misra, A., Poorsolhjouy, P.: Granular micromechanics based micromorphic model predicts frequency band gaps. *Continuum Mechanics and Thermodynamics* **28**(1-2), 215–234 (2016)
19. Nejadsadeghi, N., Placidi, L., Romeo, M., Misra, A.: Frequency band gaps in dielectric granular metamaterials modulated by electric field. *Mechanics Research Communications* (2019)
20. Lurie, S.A., Kalamkarov, A.L., Solyaev, Y.O., Ustenko, A.D., Volkov, A.V.: Continuum micro-dilatation modeling of auxetic metamaterials. *International Journal of Solids and Structures* **132**, 188–200 (2018)
21. Solyaev, Y., Lurie, S., Ustenko, A.: Numerical modeling of a composite auxetic metamaterials using micro-dilatation theory. *Continuum Mechanics and Thermodynamics* pp. 1–9 (2018)
22. Altenbach, H., Eremeyev, V.A.: On the bending of viscoelastic plates made of polymer foams. *Acta Mechanica* **204**(3), 137 (2008)
23. Altenbach, H., Eremeyev, V.: Analysis of the viscoelastic behavior of plates made of functionally graded materials. *ZAMM-Journal of Applied Mathematics and Mechanics/Zeitschrift für Angewandte Mathematik und Mechanik* **88**(5), 332–341 (2008)
24. Alibert, J.J., Seppecher, P., dell'Isola, F.: Truss modular beams with deformation energy depending on higher displacement gradients. *Mathematics and Mechanics of Solids* **8**(1), 51–73 (2003)
25. Seppecher, P., Alibert, J.J., dell'Isola, F.: Linear elastic trusses leading to continua with exotic mechanical interactions. In: *Journal of Physics: Conference Series*, vol. 319, p. 012018. IOP Publishing (2011)
26. Placidi, L., Andreas, U., Giorgio, I.: Identification of two-dimensional pantographic structure via a linear d4 orthotropic second gradient elastic model. *Journal of Engineering Mathematics* pp. 1–21 (2016)
27. dell'Isola, F., Giorgio, I., Pawlikowski, M., Rizzi, N.: Large deformations of planar extensible beams and pantographic lattices: heuristic homogenization, experimental and numerical examples of equilibrium. In: *Proc. R. Soc. A*, vol. 472, p. 20150790. The Royal Society (2016)
28. Steigmann, D., dell'Isola, F.: Mechanical response of fabric sheets to three-dimensional bending, twisting, and stretching. *Acta Mechanica Sinica* **31**(3), 373–382 (2015)
29. Turco, E., dell'Isola, F., Cazzani, A., Rizzi, N.: Hencky-type discrete model for pantographic structures: numerical comparison with second gradient continuum models. *Zeitschrift für angewandte Mathematik und Physik* **67** (2016)
30. De Angelo, M., Barchiesi, E., Giorgio, I., Abali, B.E.: Numerical identification of constitutive parameters in reduced-order bi-dimensional models for pantographic structures: application to out-of-plane buckling. *Archive of Applied Mechanics* pp. 1–26 (2019)
31. Placidi, L., Barchiesi, E., Della Corte, A.: Identification of two-dimensional pantographic structures with a linear d4 orthotropic second gradient elastic model accounting for external bulk double forces. In: *Mathematical modelling in solid mechanics*, pp. 211–232. Springer (2017)
32. Turco, E., Giorgio, I., Misra, A., dell'Isola, F.: King post truss as a motif for internal structure of (meta) material with controlled elastic properties. *Royal Society open science* **4**(10), 171153 (2017)
33. Giorgio, I., Rizzi, N., Turco, E.: Continuum modeling of pantographic sheets for out-of-plane bifurcation and vibrational analysis. *Proc. R. Soc. A* **473**(2207), 20170636 (2017)
34. Challamel, N., Kocsis, A., Wang, C.: Discrete and non-local elastica. *International Journal of Non-Linear Mechanics* **77**, 128–140 (2015)
35. Turco, E., Misra, A., Pawlikowski, M., dell'Isola, F., Hild, F.: Enhanced piola–hencky discrete models for pantographic sheets with pivots without deformation energy: Numerics and experiments. *International Journal of Solids and Structures* (2018)
36. Turco, E., Misra, A., Sarikaya, R., Lekszycki, T.: Quantitative analysis of deformation mechanisms in pantographic substructures: experiments and modeling. *Continuum Mechanics and Thermodynamics* pp. 1–15 (2018)
37. Giorgio, I.: Numerical identification procedure between a micro-cauchy model and a macro-second gradient model for planar pantographic structures. *Zeitschrift für angewandte Mathematik und Physik* **67**(4)(95) (2016)

38. Battista, A., Cardillo, C., Del Vescovo, D., Rizzi, N., Turco, E.: Frequency shifts induced by large deformations in planar pantographic continua. *Nanomechanics Science and Technology: An International Journal* **6**(2) (2015)
39. Boutin, C., Giorgio, I., Placidi, L., et al.: Linear pantographic sheets: Asymptotic micro-macro models identification. *Mathematics and Mechanics of Complex Systems* **5**(2), 127–162 (2017)
40. Eremeyev, V.A., dell'Isola, F., Boutin, C., Steigmann, D.: Linear pantographic sheets: Existence and uniqueness of weak solutions. *Journal of Elasticity* **132**(2), 175–196 (2018)
41. Rahali, Y., Giorgio, I., Ganghoffer, J., dell'Isola, F.: Homogenization à la piola produces second gradient continuum models for linear pantographic lattices. *International Journal of Engineering Science* **97**, 148–172 (2015)
42. Andreadus, U., Spagnuolo, M., Lekszycki, T., Eugster, S.R.: A ritz approach for the static analysis of planar pantographic structures modeled with nonlinear Euler–Bernoulli beams. *Continuum Mechanics and Thermodynamics* pp. 1–21 (2018)
43. Turco, E., Barcz, K., Pawlikowski, M., Rizzi, N.: Non-standard coupled extensional and bending bias tests for planar pantographic lattices. part i: numerical simulations. *Zeitschrift für angewandte Mathematik und Physik* **67**(5), 122 (2016)
44. Turco, E., Golaszewski, M., Giorgio, I., D'Annibale, F.: Pantographic lattices with non-orthogonal fibres: Experiments and their numerical simulations. *Composites Part B: Engineering* **118**, 1–14 (2017)
45. Ganzosch, G., Hoschke, K., Lekszycki, T., Giorgio, I., Turco, E., Müller, W.: 3d-measurements of 3d-deformations of pantographic structures. *TECHNISCHE MECHANIK* **38**(3), 233–245 (2018)
46. Ganzosch, G., dell'Isola, F., Turco, e., Lekszycki, T., Müller, W.: Shearing tests applied to pantographic structures. *Acta Polytechnica CTU Proceedings* **7**, 1–6 (2016)
47. Turco, E., dell'Isola, F., Rizzi, N., Grygoruk, R., Müller, W., Liebold, C.: Fiber rupture in sheared planar pantographic sheets: Numerical and experimental evidence. *Mechanics Research Communications* **76**, 86–90 (2016)
48. Barchiesi, E., dell'Isola, F., Laudato, M., Placidi, L., Seppecher, P.: A 1d continuum model for beams with pantographic microstructure: Asymptotic micro-macro identification and numerical results. In: *Advances in Mechanics of Microstructured Media and Structures*, pp. 43–74. Springer (2018)
49. Rudra, R.: A curve-fitting program to stress relaxation data. *CANADIAN AGRICULTURAL ENGINEERING* **29**(2), 209 (1987)
50. Placidi, L., Misra, A., Barchiesi, E.: Simulation results for damage with evolving microstructure and growing strain gradient moduli. *Continuum Mechanics and Thermodynamics* pp. 1–21 (2018)
51. Placidi, L., Misra, A., Barchiesi, E.: Two-dimensional strain gradient damage modeling: a variational approach. *Zeitschrift für angewandte Mathematik und Physik* **69**(3), 56 (2018)
52. Placidi, L., Barchiesi, E., Misra, A.: A strain gradient variational approach to damage: a comparison with damage gradient models and numerical results. *Mathematics and Mechanics of Complex Systems* **6**(2), 77–100 (2018)
53. Placidi, L., Barchiesi, E.: Energy approach to brittle fracture in strain-gradient modelling. *Proc. R. Soc. A* **474**(2210), 20170878 (2018)
54. Spagnuolo, M., Barcz, K., Pfaff, A., dell'Isola, F., Franciosi, P.: Qualitative pivot damage analysis in aluminum printed pantographic sheets: numerics and experiments. *Mechanics Research Communications* (2017)
55. Marmo, F., Rosati, L.: Analytical integration of elasto-plastic uniaxial constitutive laws over arbitrary sections. *International Journal for Numerical Methods in Engineering* **91**(9), 990–1022 (2012)
56. D'Annibale, F., Rosi, G., Luongo, A.: Linear stability of piezoelectric-controlled discrete mechanical systems under nonconservative positional forces. *Meccanica* **50**(3), 825–839 (2015)
57. Marmo, F., Rosati, L.: The fiber-free approach in the evaluation of the tangent stiffness matrix for elastoplastic uniaxial constitutive laws. *International Journal for Numerical Methods in Engineering* **94**(9), 868–894 (2013)

58. Marmo, F., Sessa, S., Rosati, L.: Analytical solution of the cerruti problem under linearly distributed horizontal loads over polygonal domains. *Journal of Elasticity* **124**(1), 27–56 (2016)
59. Franciosi, P.: A decomposition method for obtaining global mean green operators of inclusions patterns. application to parallel infinite beams in at least transversally isotropic media. *International Journal of Solids and Structures* **147**, 1–19 (2018)
60. Trotta, S., Marmo, F., Rosati, L.: Evaluation of the eshelby tensor for polygonal inclusions. *Composites Part B: Engineering* **115**, 170–181 (2017)
61. Franciosi, P.: Multiple continuity of phases in composite materials: Overall property estimates from a laminate system scheme. *International Journal of Solids and Structures* (2019)
62. Franciosi, P., Charles, Y.: Effective property estimates for n-phase composites with from all to none co-continuous phases. *International Journal of Solids and Structures* **96**, 110–125 (2016)
63. Franciosi, P., Charles, Y.: Mean green operators and eshelby tensors for hemispherical inclusions and hemisphere interactions in spheres. application to bi-material spherical inclusions in isotropic spaces. *Mechanics Research Communications* **75**, 57–66 (2016)
64. di Cosmo, F., Laudato, M., Spagnuolo, M.: Acoustic metamaterials based on local resonances: Homogenization, optimization and applications. In: *Generalized Models and Non-classical Approaches in Complex Materials 1*, pp. 247–274. Springer (2018)
65. Abbas, I.A., Abdalla, A.E.N.N., Alzahrani, F.S., Spagnuolo, M.: Wave propagation in a generalized thermoelastic plate using eigenvalue approach. *Journal of Thermal Stresses* **39**(11), 1367–1377 (2016)
66. Abd-allaa, A.e.n.N., Alshaikh, F., Del Vescovo, D., Spagnuolo, M.: Plane waves and eigenfrequency study in a transversely isotropic magneto-thermoelastic medium under the effect of a constant angular velocity. *Journal of Thermal Stresses* **40**(9), 1079–1092 (2017)
67. Laudato, M., Manzari, L., Barchiesi, E., Di Cosmo, F., Göransson, P.: First experimental observation of the dynamical behavior of a pantographic metamaterial. *Mechanics Research Communications* **94**, 125–127 (2018)
68. Barchiesi, E., Laudato, M., Di Cosmo, F.: Wave dispersion in non-linear pantographic beams. *Mechanics Research Communications* **94**, 128–132 (2018)