

ARTICLE

Sodium-Coupled Electron Transfer Reactivity of Metal-Organic Frameworks Containing Titanium Clusters: The Importance of Cations in Redox Chemistry

Cite this: DOI: 10.1039/x0xx00000x

Received 00th January 2012,
Accepted 00th January 2012

DOI: 10.1039/x0xx00000x

www.rsc.org/

Caroline T. Saouma,^{‡,±,∞} Chih-Chin Tsou,^{‡,δ,∞} Sarah R. Richard,[‡] Rob Ameloot,^ℓ Frederik Vermoortele,^ℓ Simon Smolders,^ℓ Bart Bueken,^ℓ Antonio DiPasquale,[⊥] Werner Kaminsky,[‡] Carolyn N. Valdez,^{‡,δ} Dirk E. De Vos,^{*,ℓ} James M. Mayer^{*,‡,δ}


Stoichiometric reduction reactions of two metal-organic frameworks (MOFs) by the solution reagents MCP*₂ (M = Cr, Co) are described. The two MOFs contain clusters with Ti₈O₈ rings: Ti₈O₈(OH)₄(bdc)₆; bdc = terephthalate (MIL-125) and Ti₈O₈(OH)₄(bdc-NH₂)₆; bdc-NH₂ = 2-aminoterephthalate (NH₂-MIL-125). The stoichiometry of the redox reactions was probed using solution NMR methods. The extent of reduction is greatly enhanced by the presence of Na⁺, which is incorporated into the bulk of the material. The roughly 1:1 stoichiometry of electrons and cations indicates that the storage of e⁻ in the MOF is tightly coupled to a cation within the architecture, for charge balance.

Introduction

Metal-organic frameworks (MOFs) are emerging as promising materials for facilitating redox reactions, including multi-e⁻/multi-H⁺ transformations. Recent studies highlight the ability of the organic linkers or the metal ions at the MOF nodes to undergo 1-e⁻ oxidations^{1–3} or reductions,^{4–6} for the MOFs themselves to serve as conductive materials^{6–12} or semiconductors,^{13–16} and for the MOFs to facilitate redox reactions that are pertinent to fuel cells and energy.^{3,17–23} MOFs are also already commercially available in Li ion batteries.^{24–27} The diversity of these studies reaffirm the promise of using MOFs in a variety of redox systems. This underscores the importance of understanding how MOFs participate in these redox processes, as well as how the change in redox state impacts the stability and reactivity of the material.^{28,29}

The well-known Ti-based MOFs MIL-125³⁰ (Ti₈O₈(OH)₄(bdc)₆) and its amino-substituted analogue NH₂-MIL-125²³ (Ti₈O₈(OH)₄(bdc-NH₂)₆) have recently been thoroughly investigated for their photo-activity (bdc = terephthalate; (bdc-NH₂ = 2-amino-terephthalate). UV

irradiation of a slurry of MIL-125 in benzyl alcohol results in oxidation of the alcohol to benzaldehyde and a color change from white to blue, due to the reduction of Ti(IV) to Ti(III).³⁰ It was suggested that this process reduces each MOF node (Ti₈ cluster) by a net H-atom (Eq 1). Using a simple solution NMR assay for titrating H-atom equivalents in MOFs, we have shown that this is indeed the case.^{5,31}



Intrigued by the stability of these MOFs to reduction, we have turned our attention to exploring the chemical reduction of MIL-125 and NH₂-MIL-125. Here, we describe a simple method to quantify the reducing equivalents added to the MOFs, and establish the importance of coupling electron transfer with cation transfer. Model studies on soluble cluster analogues suggest a specific role for Na⁺ in facilitating reduction. These fundamental studies provide new insights into the redox properties of MOFs, in particular the importance of internal charge balance.

[∞] C.T.S. and C.-C. T. contributed equally to the manuscript.

[‡] Department of Chemistry, University of Washington, Box 351700, Seattle, Washington 98195-1700, U.S.A.

^ℓ Centre for Surface Chemistry and Catalysis, KU Leuven – University of Leuven, Celestijnenlaan 200F p.o. box 2461, 3001 Leuven, Belgium, dirk.devos@kuleuven.be

[±] Department of Chemistry, University of Utah, 315 S 1400 E, Salt Lake City, Utah, 84112-0850, U.S.A., caroline.saouma@utah.edu

^δ Department of Chemistry, Yale University, P.O. Box 208107, New Haven, CT 06520-8107, james.mayer@yale.edu

[⊥] Department of Chemistry, University of California, Latimer Hall, Berkeley, CA 94720

ARTICLE

Results

Chemical Reduction with CrCp*₂

Chemical reductions of suspensions of MIL-125 and NH₂-MIL-125 were explored with the outer-sphere electron donors CrCp*₂ and CoCp*₂. These soluble reductants were chosen because they allow for quantification of the reduction stoichiometry (electrons transferred per Ti₈ node) via solution ¹H NMR spectroscopy. Both CrCp*₂/CrCp*₂⁺ and CoCp*₂/CoCp*₂⁺ undergo fast chemical exchange on the NMR timescale. Therefore solutions containing both the oxidized and reduced forms show a single resonance for MCp*₂/MCp*₂⁺ (M = Cr, Co) whose chemical shift indicates the mole fraction of each species in solution (Eq 2),³² and hence the number of e[−] transferred to MIL-125.

$$\delta_{obs} = \chi_{MCp_2^*} \delta_{MCp_2^*} + \chi_{MCp_2^{*+}} \delta_{MCp_2^{*+}} \quad (2)$$

Thus, MCp*₂ serves as both a reductant and assay for redox quantification. In these studies, suspensions of MIL-125 in solutions of MCp*₂ were stirred for ~ 12 h, after which the reactions were filtered. NMR analysis of the filtrate yields the MCp*₂/MCp*₂⁺ ratio. Combining this with the relative amounts of MCp*₂ and MIL-125 quantifies the stoichiometry of the e[−] transferred per Ti₈ node.

To establish whether MCp*₂^{+/0} is taken up in the pores of MIL-125 (5–7 Å windows),³⁰ which would render the aforementioned analysis inaccurate, uptake studies were conducted. For these studies, FeCp*₂ was used as an isosteric diamagnetic analog because the average Fe–C_{ring} bond distance of 2.05 Å in FeCp*₂ is less than those found in the MCp*₂^{+/0} analogues used in this manuscript (For CrCp*₂⁺: 2.212 Å; CrCp*₂: 2.163 Å; CoCp*₂⁺: 2.058 Å; CrCp*₂: 2.091 Å). A solution of FeCp*₂ and (*p*-tolyl)₂O as a standard in C₆D₆ was prepared and its ¹H NMR spectrum was obtained. MIL-125 was added, the suspension stirred for 3 h, and another ¹H NMR spectrum was obtained. The change in the integrals was noted. While smaller molecules such as FeCp₂ were taken up into the MOF, as evidenced by a decrease in relative integration, that of FeCp*₂ remained unchanged. Thus, we conclude that the MCp*₂^{+/0} ions cannot enter the pores of the MOFs.

Addition of CrCp*₂ to a *d*₈-THF+CD₃CN 4:1 v/v suspension of MIL-125 (1/12th equiv of CrCp*₂ per Ti₈ node) resulted in the disappearance of the ¹H NMR resonance for CrCp*₂^{+/0} and a change in solution color from yellow to very pale yellow. The

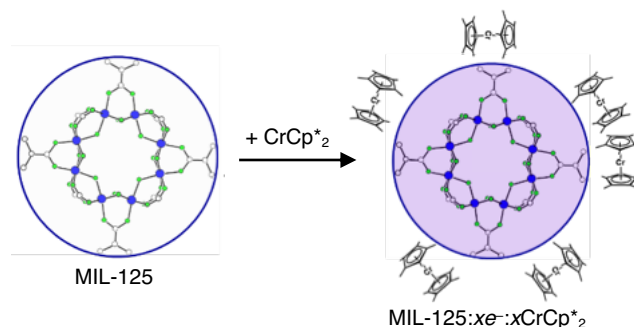


Figure 1: Reduction of MIL-125 with CrCp*₂.

solution color suggests the formation of a very small concentration of CrCp*₂⁺. Since neither CrCp*₂ or CrCp*₂⁺ is taken up in the pores of the MOF, the absence of a CrCp*₂^{+/0} in solution suggests that CrCp*₂⁺ is formed and that it ion-pairs with the reduced MIL-125 (Figure 1). The suggestion of ion pairing is supported by experiments adding 10 or 20 equiv of ⁿBu₄N⁺PF₆[−] into the 1:12 mixture of CrCp*₂:MIL-125. This resulted in the liberation of ~ 36% and 39% of CrCp*₂^{+/0}, respectively. Similar results are obtained with NH₂-MIL-125 (see ESI).

The addition of 3 equiv of CrCp*₂ per node of MIL-125 gave solutions containing only CrCp*₂. Integration of CrCp*₂ (relative to an internal standard) indicated that 0.27 equiv of CrCp*₂^{+/0} was ion-paired with the MIL-125. This represents the upper-limit for electron transfer to the MOF (batch 2) in the absence of added Na⁺ cations.

The Effect of Na⁺ on Chemical Reductions with CrCp*₂

Added Na⁺ has a strong effect on the extent of MIL-125 reduction by CrCp*₂. Owing to its solubility, commercial availability, and stability of the counter anion, NaTFSI (TFSI = bis(trifluoromethane sulfonyl)imide) was used in these studies.

As mentioned above, addition 3 equiv of CrCp*₂ to a suspension of MIL-125 in the absence of Na⁺ resulted in slight reduction of MIL-125. Addition of 0.2 to 1.0 equiv of NaTFSI into the above-mentioned mixture led to a change of the chemical shift of CrCp*₂^{+/0} from ~ −6 ppm to ~ 2 ppm, corresponding to CrCp*₂ oxidation (Figure 2). This suggests that reduction of MIL-125 is facilitated by and coupled to cation uptake, in this case, sodium, or *sodium-coupled electron transfer* (a version of ‘metal-ion coupled electron transfer’ coined by Nam and Fukuzumi for molecular reactions³³).

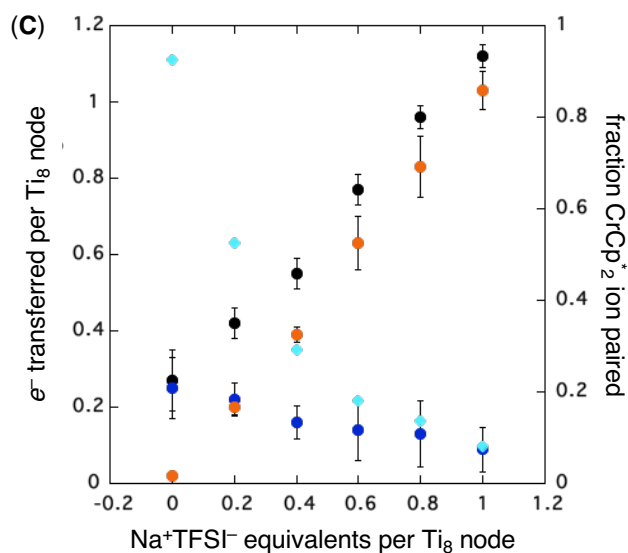
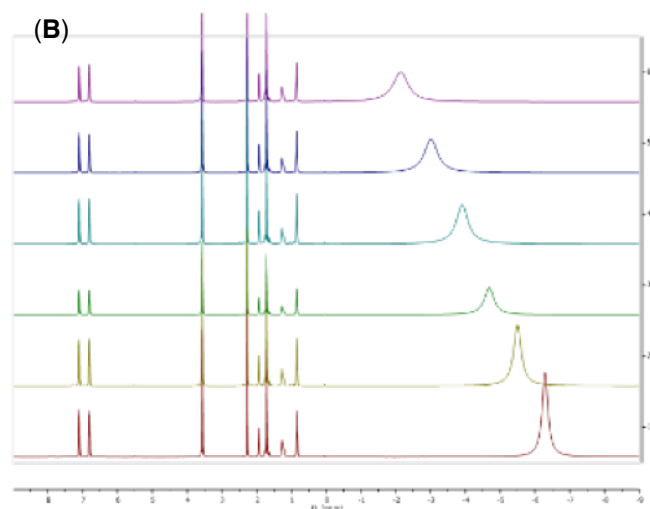
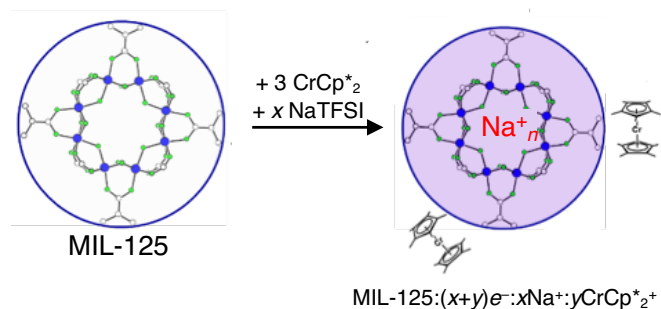


Figure 2: Reduction of MIL-125 with CrCp *_2 and Na $^+$ (NaTFSI). (A): Schematic of the reaction. (B): ^1H NMR spectra (d_8 -THF+CD $_3$ CN 4:1 v/v) of mixtures of MIL-125 + 3 equiv CrCp *_2 + different equiv of Na $^+$ per Ti $_8$ node: 0 (red), 0.2 Na $^+$ (yellow), 0.4 Na $^+$ (green), 0.6 Na $^+$ (light blue), 0.8 Na $^+$ (dark blue), and 1.0 Na $^+$ (purple). (C): Plot of e^- transferred to MIL-125 (left axis) and fraction of CrCp *_2 ion-paired in reduced MIL-125 (right axis) versus equiv NaTFSI added. Orange circles: equiv of Na $^+$ associated with the reduced MIL-125, derived from the CrCp *_2 $^{0/+}$ chemical shift. Blue circles: equiv CrCp *_2 $^+$ associated with the reduced MIL-125, derived from the change in integration of the CrCp *_2 $^{0/+}$ resonance upon mixing with MIL-125. Black circles: total extent of reduction (the sum of the blue and orange circles). Light blue diamonds: fraction of the reduced MIL-125 that is associated with CrCp *_2 $^+$.

When 1 equivalent of NaTFSI was added to a mixture of MIL-125 and CrCp *_2 , the number of electrons in the MOF increased from 0.27 ± 0.08 (with no Na $^+$) to 1.12 ± 0.03 per Ti $_8$ node. Integration of the CrCp *_2 $^{0/+}$ resonance showed that NaTFSI addition reduced the amount of the CrCp *_2 $^+$ that was ion-paired with the MOF. The ion paired CrCp *_2 $^+$ decreased from 0.25 to 0.09 equiv per Ti $_8$ node, which corresponds to a drop from 93% to 8% of the electrons being ion-paired with CrCp *_2 $^+$. Thus, 1 equivalent of Na $^+$ led to roughly 1 e^- per TiO $_8$ node and the charge balance for this added electron was provided by Na $^+$, not CrCp *_2 $^+$. These data suggest that all of the Na $^+$ is associated with the reduced MIL-125. Given that there is one electron for every node in the MOF, the cation was very likely taken up into the pores, as discussed below. Similar results were obtained for NH $_2$ -MIL-125 (see ESI). Taken together, the results show that under these conditions, MIL-125 behaves like a sodium battery, accepting electrons with sodium ions.

To determine how the amount of reductant impacts the extent of MOF reduction, 6 equiv of CrCp *_2 was added to a suspension of MIL-125. Under these conditions, with 0 and 1 equiv of NaTFSI, MIL-125 is reduced by 0.28 ± 0.07 and 1.14 ± 0.04 electrons, respectively. Thus, doubling the equiv of reductant does not impact the extent of reduction, as these values are within error of those obtained with 3 equiv of CrCp *_2 . Hence, the extent of reduction is controlled by the amount of Na $^+$, not the amount of reductant.

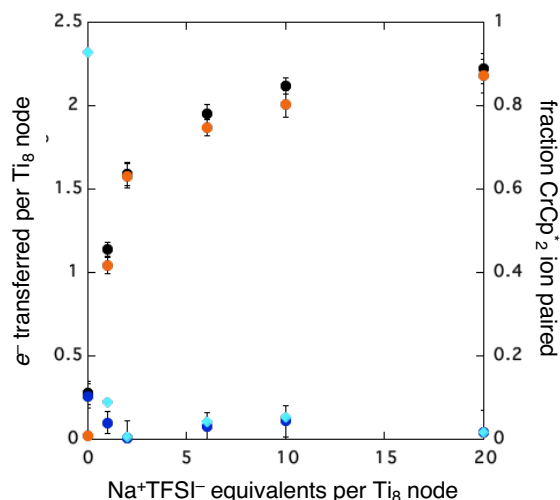


Figure 3: Reduction of MIL-125 with 6 equiv CrCp*₂ and 0-20 equiv Na⁺ in *ds*-THF+CD₃CN 4:1 v/v). Plot of e⁻ transferred to MIL-125 (left axis), and fraction of CrCp*₂ ion-paired in reduced MIL-125 (right axis), versus equiv NaTFSI added. Orange circles: equiv Na⁺ associated with the reduced MIL-125, derived from the CrCp*₂^{0/+} chemical shift. Blue circles: equiv CrCp*₂⁺ that are associated with the reduced MIL-125, derived from the change in integration of the CrCp*₂^{0/+} resonance upon mixing with MIL-125. Black circles: total extent of reduction (sum of blue and orange). Light blue diamonds represent the fraction of the reduced MIL-125 that is associated with CrCp*₂⁺.

To probe the maximum amount that MIL-125 could be reduced with CrCp*₂, excess NaTFSI was added to suspensions of MIL-125 with 6 equiv of reductant. Figure 3 shows the results of a titration: the extent of reduction versus the Na⁺ equiv added. The electrons transferred to the MOF initially rises linearly with the added Na⁺, then levels off. With 20 equiv of NaTFSI, MIL-125 is reduced by a 2.22 ± 0.09 electrons. The equiv of CrCp*₂⁺ associated with reduced MIL-125 does not significantly change with increasing Na⁺ equiv, all being within error of one another.

To probe the chemical oxidation of this reduced MOF (2.2 e⁻), the reduced MIL-125 was isolated by washing with THF+MeCN (4:1 v/v), centrifuging and removal of the solvent layer for 5 times, followed by drying under vacuum. The reduced-MIL-125 was then reacted with 4 equiv. of (FeCp*₂)PF₆ ($E^\circ = -0.48$ V vs Fc^{+/0} in MeCN), a pure 1 e⁻-acceptor, leading to bleaching of dark-purple colour of MIL-125. However, the colour of bleached MIL-125 was not perfectly white as the original one, which represents the reduced MIL-125 was not fully oxidized by (FeCp*₂)PF₆. By monitoring the change of ¹H chemical shift of FeCp*₂^{+/0}, the reaction of the reduced MIL-125 and ~ 4 equiv of (FeCp*₂)PF₆ showed that the yield of FeCp*₂ was 1.06 ± 0.19 equiv. As the reaction was further stirred for another day, the yield of FeCp*₂ just increased less than 1% (data not shown). As shown by powder X-ray diffraction data (Figures S9-S12), the structure of MIL-125 remains intact during reduction and after reoxidation.

As addition of Na⁺ triggers reduction of MIL-125, we explored the converse: whether removal of Na⁺ would cause oxidation of the MOF. To test this, varying amounts of [2.2.2]-cryptand, a strong Na⁺ chelating ligand, was added to a sample of MIL-125 which was reduced with 3 equiv CrCp*₂ in the

presence of 1 equiv NaTFSI. Prior to addition of cryptand, NMR analysis of the solution indicated that MIL-125 was reduced by 1.07 ± 0.08 electrons, which was accompanied by uptake of 0.98 ± 0.09 equiv of Na⁺ and ion-pairing of 0.09 ± 0.09 equiv of CrCp*₂⁺. Incremental addition of the cryptand resulted in a shift of the CrCp*₂^{+/0} resonance, favoring more reduced CrCp*₂. From the peak position and integration of the CrCp*₂^{+/0} resonance, the amount of reduced MIL-125 that is associated with Na⁺ and CrCp*₂ was again obtained. Figure 4 shows that addition of cryptand results in oxidation of the MOF, with 1 equiv of cryptand resulting in removal of 0.47 ± 0.10 electrons from MIL-125. As the cryptand simply removes Na⁺, the electron must go to CrCp*₂⁺. As electrons are removed upon addition of cryptand, the equiv Na⁺ associated with reduced MIL-125 decreases, as anticipated. Figure 4 also shows that addition of cryptand increases the equiv of CrCp*₂⁺ that are associated with the reduced MIL-125. In fact, with 1 equiv of cryptand, there are 0.23 ± 0.12 equiv of CrCp*₂⁺ associated with the reduced MIL-125. This is within error of the maximum value obtained when 3 equiv of CrCp*₂ was added to MIL-125 (0.25 ± 0.08).

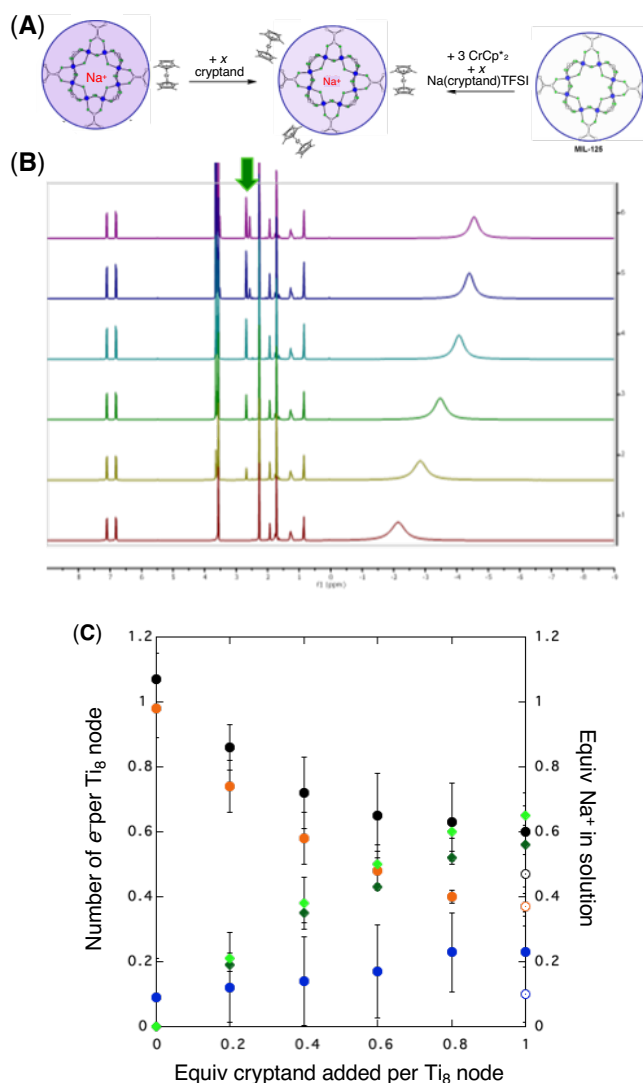


Figure 4: Effect of adding cryptand to reduced MIL-125 (3 equiv CrCp^{*2} + 1 equiv of Na^+), and reduction of MIL-125 with CrCp^{*2} and $(\text{Na}\cdot\text{cryptand})\text{TFSI}$. (A): Schematic of this reaction. (B): ^1H NMR spectra (d_8 -THF+ CD_3CN , 4:1 v/v) MIL-125 + 3 equiv CrCp^{*2} + 3 equiv NaTFSI + 0 (red), 0.2 (yellow), 0.4 (green), 0.6 (light blue), 0.8 (dark blue), and 1.0 (purple) equiv cryptand (per Ti_8 node). The two peaks indicated by the arrow correspond to free (right) and Na-bound (left) cryptand. (C): Plot of e^- in MIL-125 versus equivs of cryptand added (left axis), and equiv of Na^+ in solution (right axis). Orange circles: equivs Na^+ associated with the reduced MIL-125, derived from the $\text{CrCp}^{*2/0+}$ chemical shift. Blue circles: equivs CrCp^{*2} associated with the reduced MIL-125, derived from the change in integration of the $\text{CrCp}^{*2/0+}$ resonance. Black circles: total extent of reduction (sum of blue and orange). Light green diamonds: equiv Na^+ in solution, derived from the amount of Na^+ still associated with reduced MIL-125. Dark green diamonds: equiv of Na^+ in solution, from integration of the cryptand/cryptand-sodium resonances. Open circles: number of e^- in MIL-125 (per Ti_8 node) for the converse reaction: addition of 3 equiv of CrCp^{*2} and 1 equiv of $\text{Na}^+(\text{cryptand})\text{TFSI}^-$.

The chemical shift of the cryptand differed from that of $[\text{Na}\cdot\text{cryptand}]^+$, allowing for quantification of cryptand in solution that was bound to Na^+ . Figure 4 shows that the equiv of $[\text{Na}\cdot\text{cryptand}]^+$ from this analysis are similar to that obtained for the amount of Na^+ in solution from analysis of the $\text{CrCp}^{*2/0+}$ resonance.

The converse reaction, that is, addition of 1 equiv of $[\text{Na}\cdot\text{cryptand}]\text{TFSI}$ to a suspension of MIL-125 in a solution with 3 equiv of CrCp^{*2} was also investigated. As in the absence of cryptand, addition of Na^+ results in increased reduction of MIL-125, however, qualitatively, the reaction is slower. After ten days, MIL-125 is reduced by 0.47 ± 0.06 electrons, and the reduced material is associated with 0.37 ± 0.06 and 0.10 ± 0.08 equiv of Na^+ and CrCp^{*2+} , respectively. These values are within error of those obtained when cryptand is added to the reduced MOF. Analogous results are obtained for NH_2 -MIL-125. Thus, the various NMR measurements are all consistent with the reactions at the top of Figure 4, that the number of electrons and Na^+ ions in the MOF change in parallel.

Chemical Reduction with CoCp^{*2} with and without Na^+

To test the maximum level of charging, a sample of MIL-125 was treated with 10 equiv of NaBARF_{24} and 10 equiv CoCp^{*2} (BARF_{24} = tetrakis[(3,5-trifluoromethyl)phenyl]borate). CoCp^{*2} is a very strong soluble reductant, 0.45 V more reducing than CrCp^{*2} [$E_{1/2} = -1.91$ V for CrCp^{*2} and -1.46 V for CrCp^{*2} vs. $\text{FeCp}_2^{+/0}$ in MeCN ^{34,35}]. The NMR analysis showed 8.7 ± 0.2 equiv of e^- transferred. This roughly corresponds to every Ti center being reduced by one electron, ca. $8 e^-$ for each Ti_8O_8 cluster node.

The reaction of MIL-125 with 10 equiv CoCp^{*2} without Na^+ showed very little darkening of MIL-125. From the ^1H NMR $\text{CoCp}^{*2}/\text{CoCp}^{*2+}$ analysis, 0.05 ± 0.03 equiv of CoCp^{*2+} is formed per Ti_8 cluster. This result is an average of 6 runs, from different MIL-125 batches (*vide infra*) in which the size of crystallites varied (see ESI and Figure 5 caption).

To elaborate on the role that the cation plays on reduction of the MOF, suspensions of MIL-125 with 2 equiv of CoCp^{*2} were titrated with 0 – 2 equiv of NaBARF_{24} in THF, following the procedure described above (Figure 5). In the presence of Na^+ , an immediate color change of the solids to dark purple is observed, concomitant with lightening of the solution due to conversion of CoCp^{*2} to CoCp^{*2+} . Analysis of the $\text{CoCp}^{*2}/\text{CoCp}^{*2+}$ ratio indicates a good correlation between Na^+ equivs and the extent of reduction, across four different batches of MIL-125 (Figure 5). The solid MOF from reactions with 1 and 2 equiv of Na^+ per Ti_8O_8 cluster were also isolated, washed and analyzed by ICP. The $\text{Na}:\text{Ti}$ ratios obtained were 0.10 ± 0.03 and 0.21 ± 0.02 (using batch 4 of MIL-125). These are in agreement with the ratios expected based on the addition stoichiometry, 0.125 and 0.25 respectively.

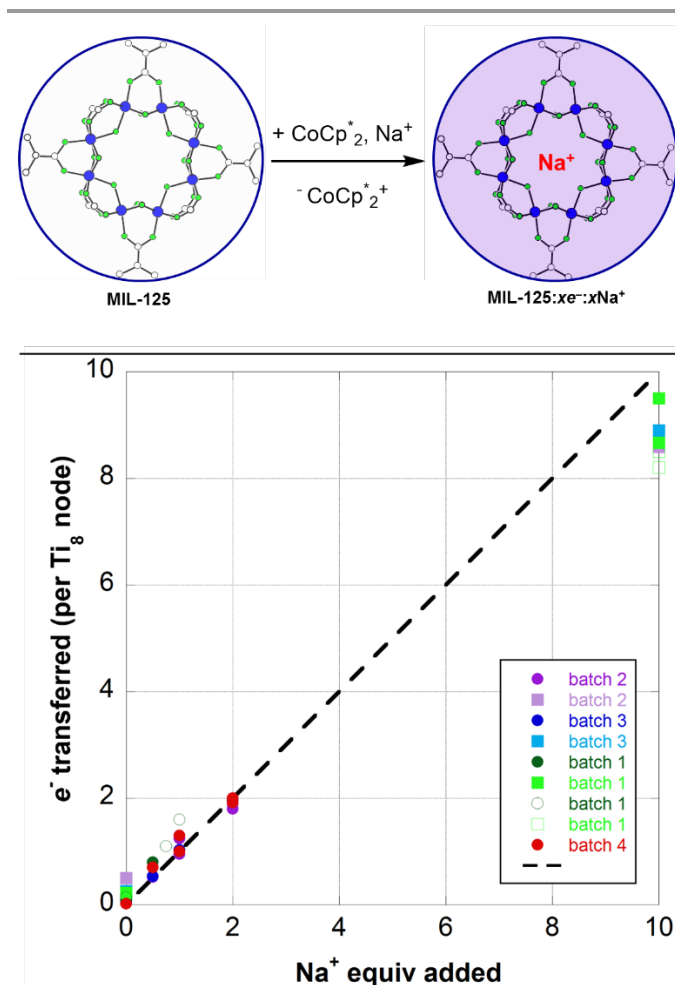


Figure 5. (Top): Schematic of the reduction of MIL-125 with CoCp^*_2 . The darkening indicates addition of electrons, and incorporation of sodium is designated by the red Na^+ . (Bottom): Extent of MIL-125 reduction versus equiv of Na^+ added to various batches of MIL-125. Experiments with 2 (circles) and 10 (squares) equiv of CoCp^*_2 are plotted. The dashed line represents a 1:1 stoichiometry, and is not a fit. Description of the MIL-125 crystallites are: batch 1 has ellipsoid morphology and axes of $300 (\pm 100) - 850 (\pm 50)$ nm; batch 2 has spherical morphology with axes of $85 (\pm 17)$ nm; batch 3 has octahedral morphology with edges of $2650 (\pm 1350)$ nm; batch 4 contains deuterated bdc linkers and has ellipsoid morphology and axes of $600 (\pm 200) - 1150 (\pm 350)$ nm.

Plotting the combined data (Figure 5) shows that the ratio of e^- added to MIL-125 to the number of Na^+ ions is close to 1:1. Thus, as in the CrCp^*_2 case above, *each Na^+ ion titrated in allows the addition of roughly one e^- to the MOF.*

The close correlation of e^- and Na^+ stoichiometry prompted us to re-examine the observation of a small amount of electron transfer to the MOF in the absence of added cations. ICP analysis for Na and Ti was done on batch 2 of as-prepared MIL-125 and gave a Na:Ti ratio of 0.01 ± 0.02 . This amount could account for the extent of MOF reduction observed in the absence of added Na^+ . The uncertainty in the ICP measurement is significant due to the correction for the sodium background (it is ubiquitous in the environment; see ESI). The presence of CoCp^*_2 in solution in these experiments suggests the presence of a trace cation or

acid (H^+) impurity; if this were not the case, then all of the CoCp^*_2 would be tightly ion-paired with the MOF and hence would not be detected in ^1H NMR spectra.


The EPR spectra of the 1, 2, and ~ 8 -electron reduced MOF were similar to that of the photoreduced MIL-125 (see ESI). The rhombic signal broadens with increased extent of reduction, consistent with increased spin-spin interactions. Also, powder XRD patterns of the reduced materials indicate that the structure of MIL-125 is predominantly intact. Interestingly, upon reduction MIL-125's unit cell is found to slightly contract along its c-axis, while featuring a small expansion in the ab-plane. At higher reduction levels, a few additional reflections are observed. Through Pawley fitting, these reflections were found to be forbidden for MIL-125 (Figures S9-11) and may indicate some structural lability under reduction with CoCp^*_2 . These additional reflections are not observed in the case of reduction with CrCp^*_2 (FIGURE S8). For all chemically reduced samples described above, exposure to air restores the white color of oxidized MIL-125.

To probe whether e^-/Na^+ reduction occurred only at the surface or throughout the bulk of MIL-125, we examined chemical reductions using batches of the MOF that differed in their size and morphology. The smallest crystals (batch 2) were roughly spherical with a diameter of 85 ± 16.5 nm, and the largest (batch 3) were octahedral, with axes of 3650 ± 1350 nm. If reduction were limited to the surface Ti_8 clusters, then these two batches should have given different extents of reduction of MIL-125, measured as the number of e^- per Ti_8 node in the entire sample. However, the extent of reduction does not depend on the crystal size (Figures 5 and 6). This shows that reduction is not dependent on external surface area, that it is occurring at all of the nodes throughout the MOF. Thus, the e^-/Na^+ can migrate into the MOF pores. This conclusion is consistent with the very high level of reduction observed, 1-8 e^- per Ti_8 node throughout the bulk of the material. There are simply not enough Ti_8 clusters at the crystal surface to accept that many electrons, given the small ratio of surface to bulk for these sized crystals.

Soluble Cluster Analogues

To better understand the redox chemistry at a molecular level, soluble cluster analogues were prepared and studied. $\text{Ti}_8\text{O}_8(\text{OOC}^t\text{Bu})_{16}$ (**1**) was prepared as described³⁶ and isolated as a white crystalline solid. Cluster **1** is comprised of eight roughly octahedral Ti(IV) centers arranged in a cyclic array, with each Ti linked to its neighbors by one oxo and two pivalate ($^t\text{BuCOO}^-$) bridging ligands. The solution ^1H NMR spectrum (d_8 -toluene) of **1** features two sharp resonances at 1.34 and 1.22 ppm corresponding to ^tBu groups that are axial and equatorial with respect to the planar Ti_8 ring. The ligand arrangement differs from that of the nodes in MIL-125 in that the latter has four of the carboxylates replaced by bridging hydroxo groups to give an empirical cluster formula of $\text{Ti}_8\text{O}_8(\text{OH})_4(\text{OOCR})_{12}$. Also, **1** features alkyl carboxylates rather than aryl carboxylates as found in MIL-125. While the molecular cluster with benzoate ligands can be prepared,³⁶ the limited solubility and uninformative ^1H

NMR spectrum of $\text{Ti}_8\text{O}_8(\text{OOCPh})_{16}$ makes it unsuitable for these studies.

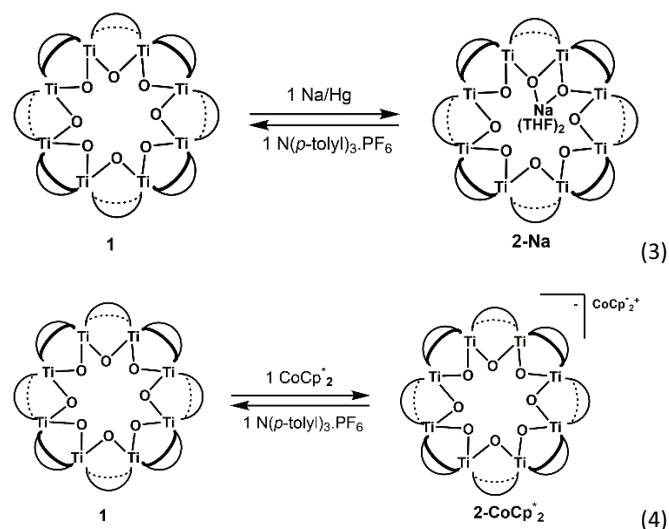

Syntheses of one-electron reduced congeners of **1** are readily achieved by treatment of **1** with 1 equiv of an appropriate reductant. Thus, stirring a THF solution of **1** over 1 equiv of Na/Hg for 6 hours results in a color change from white to blue and formation of **2-Na** (Eq 3). Addition of 1 equiv of CoCp^*_2 to a benzene solution of **1** also results in a color change to blue, with formation of the related $1 e^-$ -reduced congener, **2-CoCp*₂** (Eq 4). Both of these clusters have been thoroughly characterized (see ESI), including by single-crystal X-ray diffraction (Figure 6). Treatment of either **2-Na** or **2-CoCp*₂** with 1 equiv of the aminium oxidant $[(p\text{-tolyl})_3\text{N}^+]\text{PF}_6^-$ quantitatively converts them back to **1** (by ^1H NMR spectroscopy in d_8 -THF).

The X-ray crystal structure of **2-Na** shows that the Ti_8 ring is intact, albeit distorted, with a Na^+ cation coordinated on one edge of the inside of the ring. The Na^+ coordinates two THF molecules and the two μ -oxo ligands that flank Ti6. The Ti6-O distances of 1.9556(26) and 1.9473(27) Å are ~ 0.12 Å elongated from the mean Ti-O distance in **1** ($\text{Ti-O}_{\text{ave}} = 1.827$ Å; see Figure 6).²⁷ Moving around the ring from Ti6 the Ti-O distances alternate long and short. Next to Ti6 this difference is quite pronounced, with the two Ti-O distances for Ti5 and Ti7 differing by ~ 0.15 Å. At Ti2 on the other side of the ring, however, the two Ti-O distances are almost the same, 1.7939(24) vs. 1.8090(25) Å, and are even shorter than the average in the fully oxidized **1**. These metrical parameters indicate that the added electron is mostly localized on Ti6 in the solid-state, near the Na^+ , but that the influence of the added electron is clearly felt in the neighbouring octahedra. The addition of the Na^+ renders the ring more elliptical, with distances between titanium atoms that are across the ring varying by 0.584 Å in **2-Na** (vs. only 0.268 Å in **1**).

The structure of **2-CoCp*₂** reveals no direct interaction between the anion and cation. In the cluster anion (Figure 6 bottom), a 4-fold axis renders pairs of Ti atoms equivalent about the core. Here too, the Ti-O distances alternate between long and short, though the metrical parameters clearly show that all Ti are

equivalent; the electron is delocalized. Twinning and disorder in the CoCp^*_2 cation prevent obtaining its accurate bond metrics.

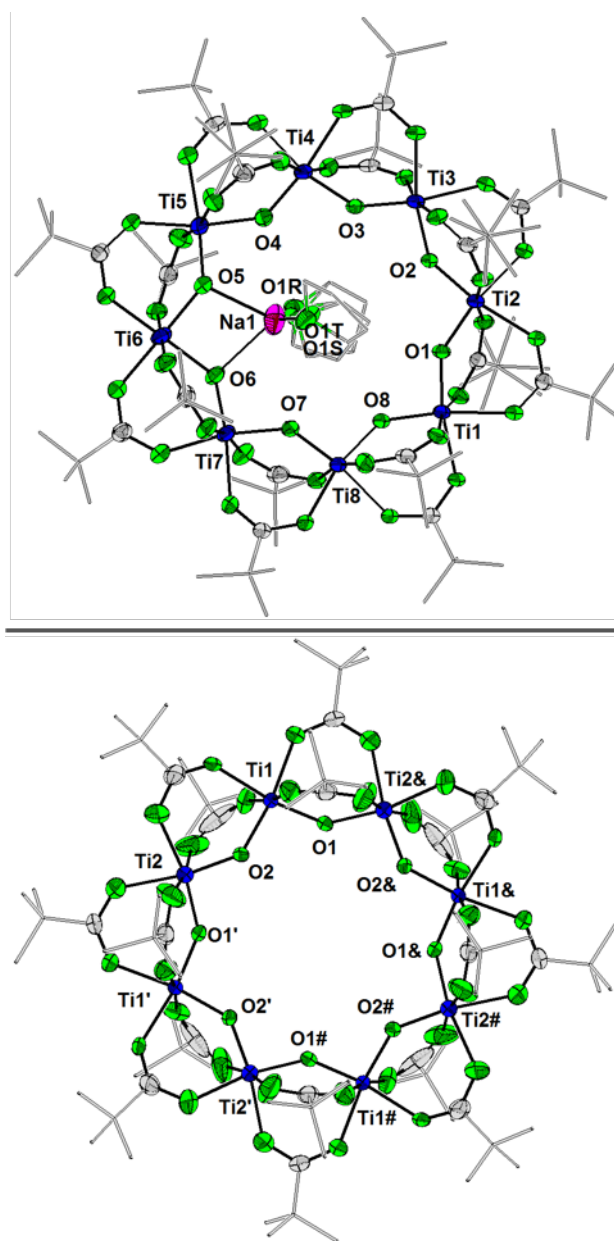


Figure 6. Displacement ellipsoid (50%) representation of (top) **2-Na** and (b) the anion of **2-CoCp*₂**. For clarity, H-atoms are omitted and $t\text{Bu}$ groups are shown as sticks. There are two THF ligands to Na^+ that are disordered, as shown (S: 24.5%, R: 75.5%); see the ESI. Select bond distances (Å) for **2-Na**: Ti1-O8 1.7796(25), Ti1-O1 1.8090(24), Ti2-O1 1.8090(25), Ti2-O2 1.7939(24), Ti3-O2 1.8285(24), Ti3-O3 1.7660(25), Ti4-O3 1.8634(25), Ti4-O4 1.7456(27), Ti5-O4 1.9075(26), Ti5-O5 1.7451(28), Ti6-O5 1.9473(27), Ti6-O6 1.9556(26), Ti7-O6 1.7346(27), Ti7-O7 1.8830(26), Ti8-O7 1.7571(25), Ti8-O8 1.8459(25). Select bond distances (Å) for **2-CoCp*₂**: Ti1-O2 1.8445(1), Ti1-O1 1.7990(1), Ti2-O1' 1.8514(1), Ti2-O2 1.7666(1).

The solution ^1H NMR spectrum of **2-CoCp*₂** in d_8 -THF consists of two paramagnetically shifted and broadened resonances at 1.373 and 1.217 ppm, which correspond to the $t\text{Bu}$ protons of the cluster. The ^1H NMR spectrum of **2-Na** (d_8 -THF) likewise features two broadened resonances at 1.415 and 1.234

ppm. To determine whether these resonances correspond to all 144 pivalate protons of the cluster or just to only protons from ^tBu protons that are distant from the odd electron, an NMR sample of **2-Na** in *d*₈-THF was oxidized with 1 equiv of [(*p*-tolyl)₃N⁺]⁺PF₆⁻. The integrals of the ^tBu resonances were the same versus an internal standard before and after oxidation, indicating that all ^tBu groups are observed in the ¹H NMR spectrum of **2-Na**. These results show that for both **2-Na** and **2-CoCp*₂**, the added electron is delocalized around the ring on the NMR timescale in solution. For **2-Na** in C₆D₆, where the Na⁺ must be closely associated with the anionic Ti₈O₈ ring, this requires that there be rapid migration of the Na⁺ around the cluster ring. This contrasts with the localization of the Na(THF)₂⁺ unit in the solid-state, as discussed above.

Discussion

MIL-125 and NH₂-MIL-125 have previously been shown to be redox-active, like other titanium-oxo containing MOFs.^{23,30,37,38} UV irradiation (or visible for the amino derivative) in the presence of an alcohol causes reduction of the MOF, as indicated by the blue colour of the reduced material. EPR spectroscopy suggests that the reduction is Ti-based.^{5,23,30} We have recently shown that this reduction corresponds to a maximum of ~2 *e*⁻ per Ti₈O₈ node. That reduction is a proton-coupled electron transfer (PCET) process, so each Ti₈ cluster is reduced by (*e*⁻ + H⁺), a net H-atom.³¹ Similar chemistry was shown for the COK-69 MOF that contains a [Ti^{IV}₃(μ³-O)(O)₂(RCOO)₆] cluster at each node.⁵

The studies reported here provide a detailed look at the cation-coupled reduction of MIL-125 and NH₂-MIL-125. Using organometallic, soluble reductants and Na⁺ salts, and with the preparation of molecular versions of the reduced Ti₈O₈ nodes, this work provides an unusually detailed and quantitative view of the reduction of a MOF.

A simple ¹H NMR assay to measure the redox stoichiometry in MOF redox reactions.

A ¹H NMR spectroscopic assay was first developed to determine the number of electrons added to a known weight of the MOF. By using bulky soluble reductants, CrCp*₂ and CoCp*₂, it was shown that the reductant is not taken up into the pores of MIL-125. Then ¹H NMR spectra reveal the concentrations of reduced and oxidized forms, MCp*₂^{0/+}. In this case, both CoCp*₂^{0/+} and CrCp*₂^{0/+} undergo fast chemical exchange, so a single resonance is observed, with the resonance position indicative of the mole fraction of each species (Eq 2). The ¹H NMR spectra showed no additional resonances, indicating the absence of decomposition of the MIL-125 or MCp*₂^{0/+} (M = Cr, Co). This assay should be widely applicable to redox reactions of materials as long as the reagent has a well-defined and well-positioned redox couple that undergoes clean reactivity and whose components do not all adsorb strongly on or in the material. Though there are now quite a few examples of redox-active MOFs, the extent of oxidation/reduction is often not

quantified. An early exception was the work of de Combarieu *et al.* showing electrochemically that an iron MOF could absorb 0.6 equiv of Li with reduction of Fe³⁺ to Fe²⁺.²⁷ Other studies of MOF battery materials have followed.²⁵ ¹H NMR spectroscopy has been used to quantify the oxidation of linkers in Mn-MOF-74 by the Dincă group.¹ Such ¹H NMR assays are typically only applicable when there is a substantial amount of redox change; they would be challenging for 0.1% doping of a semiconducting MOF, for example.

Reduction occurs throughout the MOF, not just at the surface

Treatment of MIL-125 with MCp*₂ and a soluble Na⁺ source gave substantial charging of the MOF. With 1 equivalent of Na⁺ per Ti₈O₈ node, ¹H NMR studies indicated roughly one electron per Ti₈O₈ cluster had been transferred to the MOF. With additional Na⁺, the MIL-125 may be reduced by up to 2 electrons per Ti₈ node with CrCp*₂ and up to a remarkable 8 electrons per node with CoCp*₂.

These very high charging levels are consistent only with reduction throughout the MIL-125 crystallites. There are simply not enough titanium ions in the surface layer of the MOF to accommodate all of these electrons (in the limit of 8 *e*⁻ per node, formally every titanium has been reduced to Ti(III)). In addition, different batches of MIL-125 with different sizes and morphologies behave very similarly, showing that reduction is not simply a surface property. This reduction throughout the material, as discussed in the next section, is possible because the Na⁺ ions migrate into the pores to provide local charge balance for the added electrons.

Roughly 1:1 Na⁺ to *e*⁻ stoichiometry of MIL-125 Reduction

Titration experiments adding aliquots of Na⁺ to suspensions of MIL-125 with excess MCp*₂ showed an equimolar increase in the number of electrons transferred to the MOF (a few electrons were transferred in the absence of Na⁺; see below). For instance, Figures 5 and 6 show that the extent of reduction of MIL-125 with CoCp*₂ is equal to the amount of Na⁺ up to 2 equiv of Na⁺. This is true when 2 or 10 equiv of CoCp*₂ is used, and with any of four distinct batches of MIL-125 are used. These batches differ in their size, morphology, and in one case, feature deuterated bdc linkers. Thus, the effect of Na⁺ on extent of reduction is not an artefact of one batch. The data are clear that *the Na⁺ cation controls the extent of reduction*. This 1:1 stoichiometry based on the total amount of Na⁺ added and the total number of Ti₈O₈ nodes is consistent with the conclusion that the electrons and Na⁺ ions penetrate throughout the MOF. The CoCp*₂⁺ cation is too large to enter MIL-125 and therefore cannot provide Coulombic stabilization proximal to each node as Na⁺ can. Therefore CoCp*₂⁺ cation can only stabilize a small amount of reduction of the MOF.

Control by the sodium cation is further evident in the experiment where Na⁺ was removed from the MOF. A sample of MIL-125 was equilibrated with CrCp*₂ and NaTFSI, resulting in substantial electron transfer to the MOF (Figure 4). Addition of cryptand to this mixture resulted in removal of some of the Na⁺ from the reduced MIL-125, as evidenced by the observation of

[Na⁺cryptand]⁺ in NMR spectra. Removal of the Na⁺ resulted in back electron transfer to the CrCp²⁺ present in the solution, with oxidation of the reduced MOF. Cation control of electron transfer works in both directions, as adding Na⁺ leads to MOF reduction and removing the cation causes MOF oxidation. Despite the emphasis on the electron in the language used (“oxidation and reduction”), the cation is the key actor.

The cryptand does not remove all of the Na⁺, likely due this being an equilibrium process. Some insight into the binding of Na⁺ in MIL-125 is provided by the synthesis and characterization of molecular analogues of the Ti₈O₈ MOF nodes. The crystal structure of **2-Na** shows the sodium ion chelated by two oxide ligands to a single titanium ion, which is likely to have the highest Ti(III) character. However, NMR spectra of the molecular clusters in solution show that the sodium is rapidly moving around the Ti₈O₈ ring such that the high symmetry of the oxidized form is retained. This molecular material likely gives a detailed sense of what is likely occurring inside MIL-125 + (Na⁺ + e⁻), including the low barrier to Na⁺ migration around the Ti₈O₈ ring. A similar mode of cation coordination has been suggested to occur in the electrochemical lithiation of UiO-66 (Zr₆O₄(OH)₄(bdc)₆).³⁹

The structure of the molecular anion with a decamethylcobaltocenium anion, **2-CoCp²⁺**, shows no close contacts between the anion and cation, and a more delocalized anion. The solid is an ionic solid, a 3D lattice of [2⁻] and CoCp²⁺. These are of course in a 1:1 ratio in the solid, as the unit cell of all ionic compounds must have no net charge. The same thermodynamic preference for charge balance likely drives the 1:1 stoichiometry of Na⁺ to electrons. This is especially important at the high charging levels reached here, where essentially every Ti₈O₈ unit has been reduced by at least one electron. These MOFs are behaving just like the oxide cathodes of lithium ion batteries, which have a 1:1 stoichiometry of e⁻:Li⁺, for the same reason.

MIL-125 Reduction in the absence of added Na⁺

Some electron transfer to MIL-125 is observed upon its reaction with CrCp²⁺ in the absence of Na⁺. With 3 equiv of CrCp²⁺, roughly ~0.25 equiv of electrons were transferred. Reaction with a small amount of CrCp²⁺ results in loss of the CrCp^{2+/0+} ¹H NMR signal, because of ion-pairing to the reduced MOF. The CrCp²⁺ can be in part displaced by addition of the inert salt ¹⁸Bu₄N⁺PF₆⁻ which can also engage in ion pairing. Since the CrCp²⁺ is too large to fit in the pores, electrons can be accommodated only in surface layers of the MOF, and only a limited number of electrons can be transferred.

Studies done with CoCp²⁺ as a reductant in most ways closely paralleled those done with CrCp²⁺. In some cases, however, some CoCp²⁺ could be observed when small amounts of CoCp²⁺ were used in the absence of Na⁺. This may be due to the higher sensitivity of the ¹H NMR experiment for the sharp diamagnetic signal for CoCp²⁺ versus the broad paramagnetic signal of the chromium analogue. In one of these solutions, ICP analysis provided evidence for a small amount of sodium in the reduced MIL-125. Sodium is ubiquitous in the environment, for example on glass surfaces, and could be present in sufficient trace

amounts to account for the CoCp²⁺ observed. Particularly at low concentrations or low charging levels, we caution other researchers to be wary of the large influence of trace Na⁺ or trace acid (H⁺).

Effect of the reductant; stability of the reduced MOF

As emphasized above, both CoCp²⁺ and CrCp²⁺ transfer electrons to MIL-125 in a roughly 1:1 stoichiometry with the amount of Na⁺ present. The fact that CoCp²⁺ is a much stronger reducing agent, by about -0.45 V, has no effect on this stoichiometry. However, the higher reducing power of CoCp²⁺ does change the overall extent to which MIL-125 can be reduced. Reductions with CrCp²⁺ proceed only to ca. 2 electrons per Ti₈O₈ node, even the presence of excess reductant and excess Na⁺ (Figure 3). Using CoCp²⁺, in contrast, allows the addition of ~8 electrons per node (perhaps with a small amount of decay of the MOF). This suggests that (e⁻ + Na⁺) can be added into MIL-125 up to a certain concentration that is set by the thermodynamic reducing power of the reductant.

Conclusions

The stoichiometric addition of electrons and sodium ions to the MOFs MIL-125 and NH₂-MIL-125 has been examined in detail. A simple solution NMR assay was developed, in concert with titration experiments, to separately quantify the e⁻ and Na⁺ stoichiometries. This assay should be widely applicable to other MOFs and heterogeneous solids. MIL-125 show little reactivity with the metallocene reductants CrCp²⁺ and CoCp²⁺ alone. Addition of Na⁺ cations to the suspensions, however, led to substantial reduction of the MOF. Clean and reversible reduction of the MIL-125 has been observed up to 1 (e⁻ + Na⁺) per Ti₈O₈ node. This high charging amount, and studies with MIL-125 crystallites of different sizes, show that reduction occurs at each node throughout the MOF. Molecular analogues of the reduced Ti₈O₈ nodes have been prepared and their X-ray crystal structures show that Na⁺ binds inside these clusters while MCp²⁺ does not.

The number of e⁻ added to the MOF closely parallels the number of Na⁺ added. Addition of cryptand to remove the Na⁺ from the MOF results in the corresponding transfer of e⁻ back to CrCp²⁺. In the presence of excess CoCp²⁺ and Na⁺, MIL-125 can be reduced up to 8 e⁻ per Ti₈ node. These data show that reduction of the MOF is controlled by the number of Na⁺. Only limited reduction occurs in the absence of Na⁺ since the MCp²⁺ cations are too large to fit in the pores of the MOF. This study thus shows the critical role of charge balance by the cation that accompanies the electron, a principle that is likely to be general for MOFs and many other redox-active materials.

Acknowledgment

C.T.S. gratefully acknowledges financial support from the U.S. National Institute of Health, postdoctoral fellowship

1F32GM099316. J.M.M. thanks the U.S. National Science Foundation for support via awards CHE-1151726 and CHE-1609434. S.S., B.B. and D.D.V. gratefully acknowledge the FWO for funding (Aspirant, post-doctoral grant and project funding).


Electronic Supporting Information

Additional experimental descriptions and data can be found in the Electronic Supporting Information (ESI) that accompanies this article. Data for the two x-ray crystal structures reported can be found as CCDC 1868235 and CCDC 1868236.

References

- 1 A. F. Cozzolino, C. K. Brozek, R. D. Palmer, J. Yano, M. Li and M. Dincă, *J. Am. Chem. Soc.*, 2014, **136**, 3334–3337.
- 2 Y. Tulchinsky, C. H. Hendon, K. A. Lomachenko, E. Borfecchia, B. C. Melot, M. R. Hudson, J. D. Tarver, M. D. Korzyński, A. W. Stubbs, J. J. Kagan, C. Lamberti, C. M. Brown and M. Dincă, *J. Am. Chem. Soc.*, 2017, **139**, 5992–5997.
- 3 M. L. Aubrey and J. R. Long, *J. Am. Chem. Soc.*, 2015, **137**, 13594–13602.
- 4 S. Smolders, K. A. Lomachenko, B. Bueken, A. Struyf, A. L. Bugaev, C. Atzori, N. Stock, C. Lamberti, M. B. J. Roeffaers and D. E. De Vos, *ChemPhysChem*, 2017, **19**, 373–378.
- 5 B. Bueken, F. Vermoortele, D. E. P. Vanpoucke, H. Reinsch, C.-C. Tsou, P. Valvekens, T. De Baerdemaeker, R. Ameloot, C. E. A. Kirschhock, V. Van Speybroeck, J. M. Mayer and D. De Vos, *Angew. Chemie Int. Ed.*, 2015, **54**, 13912–13917.
- 6 D. Feng, T. Lei, M. R. Lukatskaya, J. Park, Z. Huang, M. Lee, L. Shaw, S. Chen, A. A. Yakovenko, A. Kulkarni, J. Xiao, K. Fredrickson, J. B. Tok, X. Zou, Y. Cui and Z. Bao, *Nat. Energy*, 2018, **3**, 30–36.
- 7 A. Morozan and F. Jaouen, *Energy Environ. Sci.*, 2012, **5**, 9269.
- 8 M. L. Aubrey, B. M. Wiers, S. C. Andrews, T. Sakurai, S. E. Reyes-Lillo, S. M. Hamed, C.-J. Yu, L. E. Darago, J. A. Mason, J.-O. Baeg, F. Grandjean, G. J. Long, S. Seki, J. B. Neaton, P. Yang and J. R. Long, *Nat. Mater.*, 2018, **17**, 625–632.
- 9 J. A. DeGayner, I.-R. Jeon, L. Sun, M. Dincă and T. D. Harris, *J. Am. Chem. Soc.*, 2017, **139**, 4175–4184.
- 10 L. S. Xie, L. Sun, R. Wan, S. S. Park, J. A. DeGayner, C. H. Hendon and M. Dincă, *J. Am. Chem. Soc.*, 2018, **140**, 7411–7414.
- 11 L. Sun, M. G. Campbell and M. Dincă, *Angew. Chemie Int. Ed.*, 2016, **55**, 3566–3579.
- 12 L. Sun, C. H. Hendon, M. A. Minier, A. Walsh and M. Dincă, *J. Am. Chem. Soc.*, 2015, **137**, 6164–6167.
- 13 D. Sheberla, L. Sun, M. A. Blood-Forsythe, S. Er, C. R. Wade, C. K. Brozek, A. Aspuru-Guzik and M. Dincă, *J. Am. Chem. Soc.*, 2014, **136**, 8859–8862.
- 14 M. Alvaro, E. Carbonell, B. Ferrer, F. X. Llabrés i Xamena and H. Garcia, *Chemistry*, 2007, **13**, 5106–12.
- 15 M. Usman, S. Mendiratta and K.-L. Lu, *Adv. Mater.*, 2016, **29**, 1605071.
- 16 I. Stassen, N. Burtch, A. Talin, P. Falcato, M. Allendorf and R. Ameloot, *Chem. Soc. Rev.*, 2017, **46**, 3185–3241.
- 17 N. Kornienko, Y. Zhao, C. S. Kley, C. Zhu, D. Kim, S. Lin, C. J. Chang, O. M. Yaghi and P. Yang, *J. Am. Chem. Soc.*, 2015, **137**, 14129–14135.
- 18 Y. Fang, Y. Ma, M. Zheng, P. Yang, A. M. Asiri and X. Wang, *Coord. Chem. Rev.*, 2018, **373**, 83–115.
- 19 J. Zhou and B. Wang, *Chem. Soc. Rev.*, 2017, **46**, 6927–6945.
- 20 A. Mahmood, W. Guo, H. Tabassum and R. Zou, *Adv. Energy Mater.*, 2016, **6**, 1600423.
- 21 H. Wang, Q.-L. Zhu, R. Zou and Q. Xu, *Chem*, 2017, **2**, 52–80.
- 22 Y. Zhao, Z. Song, X. Li, Q. Sun, N. Cheng, S. Lawes and X. Sun, *Energy Storage Mater.*, 2016, **2**, 35–62.
- 23 Y. Fu, D. Sun, Y. Chen, R. Huang, Z. Ding, X. Fu and Z. Li, *Angew. Chemie - Int. Ed.*, 2012, **51**, 3364–3367.
- 24 Z. Peng, X. Yi, Z. Liu, J. Shang and D. Wang, *ACS Appl. Mater. Interfaces*, 2016, **8**, 14578–14585.
- 25 L. Wang, Y. Han, X. Feng, J. Zhou, P. Qi and B. Wang, *Coord. Chem. Rev.*, 2016, **307**, 361–381.
- 26 X. Lou, Y. Ning, C. Li, M. Shen, B. Hu, X. Hu and B. Hu, *Inorg. Chem.*, 2018, **57**, 3126–3132.
- 27 G. de Combarieu, M. Morcrette, F. Millange, N. Guillou, J. Cabana, C. P. Grey, I. Margiolaki, G. Férey and J.-M. Tarascon, *Chem. Mater.*, 2009, **21**, 1602–1611.
- 28 D. M. D'Alessandro, *Chem. Commun.*, 2016, **52**, 8957–8971.
- 29 S. Lin, P. M. Usov and A. J. Morris, *Chem. Commun.*, 2018, **54**, 6965–6974.
- 30 M. Dan-Hardi, C. Serre, T. Frot, L. Rozes, G. Maurin, C. Sanchez, G. Férey and G. Maurin, *J. Am. Chem. Soc.*, 2009, **131**, 10857–10859.
- 31 C. T. Saouma, S. Richard, S. Smolders, R. Ameloot, F. Vermoortele, D. E. De Vos and J. M. Mayer, *Submitted*.
- 32 J. Sandström, *Dynamic NMR Spectroscopy*, 1982.
- 33 Y. Morimoto, H. Kotani, J. Park, Y.-M. Lee, W. Nam and S. Fukuzumi, *J. Am. Chem. Soc.*, 2011, **133**, 403–405.
- 34 N. G. Connelly and W. E. Geiger, *Chem. Rev.*, 1996, **96**, 877–910.
- 35 C. N. Valdez, A. M. Schimpf, D. R. Gamelin and J. M. Mayer, *J. Am. Chem. Soc.*, 2016, **138**, 1377–1385.
- 36 T. Frot, S. Cochet, G. Laurent, C. Sassoie, M. Popall, C. Sanchez and L. Rozes, *Eur. J. Inorg. Chem.*, 2010, **8**, 5650–5659.
- 37 H. L. Nguyen, F. Gándara, H. Furukawa, T. L. H. Doan, K. E. Cordova and O. M. Yaghi, *J. Am. Chem. Soc.*, DOI:10.1021/jacs.6b01233.
- 38 J. Castells-Gil, N. M. Padial, N. Almora-Barrios, J. Albero, A. R. Ruiz-Salvador, J. González-Platas, H. García and C. Martí-Gastaldo, *Angew. Chemie*, 2018, **130**, 8589–8593.
- 39 B. Tang, S. Huang, Y. Fang, J. Hu, C. Malonzo, D. G. Truhlar and A. Stein, *J. Chem. Phys.*, 2016, **144**, 194702.

ARTICLE

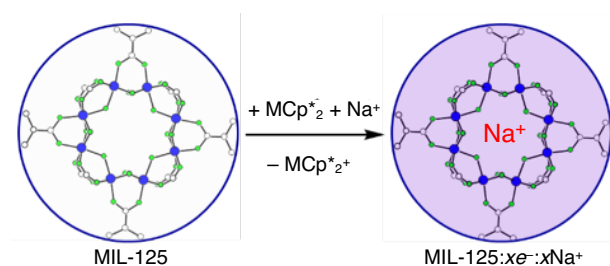Table of Contents Graphic and Text

Storage of electrons in the Ti₈O₈ nodes of MOF MIL-125 is controlled by the presence of charge-balancing Na⁺ cations.