

A Nickel-Doped Dehydrobenzoannulene-Based Two-Dimensional Covalent Organic Framework for the Reductive Cleavage of Inert Aryl C–S Bonds

W. Karl Haug, Eric R. Wolfson, Blake T. Morman, Christine M. Thomas, and Psaras L. McGrier*



Cite This: <https://dx.doi.org/10.1021/jacs.0c01026>



Read Online

ACCESS |



Metrics & More



Article Recommendations



Supporting Information

ABSTRACT: The development of metalated covalent organic frameworks (COFs) is useful for generating recyclable catalytic systems for practical applications. Herein, we report the synthesis, characterization, and catalytic properties of an azine-linked two-dimensional (2D) COF containing nickel-doped dehydrobenzoannulene (DBA) units. We demonstrate that Ni-DBA-2D-COF can be used to reductively cleave the aryl C–S bonds of several organosulfur compounds utilizing dimethylethylsilane as the reducing agent. The Ni-DBA-2D-COF catalytic system displays excellent recyclability and good yields. This work highlights a rare example of utilizing metalated DBA complexes to perform catalytic transformations.

The reductive cleavage of C–S bonds (i.e., hydrodesulfurization (HDS)) plays a pivotal role in removing sulfur impurities from petroleum feedstocks to produce clean chemical fuels.¹ The C–S bonds of organosulfur compounds can also be utilized as cleavable directing groups to help produce synthetic precursors.² While both chemical transformations are often accomplished using expensive transition metals (i.e., Pd,³ Rh,⁴ etc.), it is much more desirable to use cheap earth-abundant metals such as Ni, which are less toxic and more environmentally friendly. Interestingly, Vicic and Jones have shown⁵ that the HDS of thiophene can be achieved by using a [(dippe)NiH]₂ nickel hydride dimer and hydrogen gas as the reducing agent. Alternatively, Martin and co-workers have demonstrated⁶ that unactivated aryl C–S bonds can be reductively cleaved using a bis(1,5-cyclooctadiene)nickel(0) (Ni(COD)₂) complex and hydrosilanes as the reducing agents. While both reactions are effective under homogeneous conditions, complications associated with catalyst stability, recyclability, and catalyst separation are still a challenge. Although Raney nickel has been utilized for many decades as an effective heterogeneous catalyst for the reductive cleavage of C–S bonds,^{7,8} the efficiency of the catalyst significantly decreases after the first reduction. Thus, it is advantageous to develop novel heterogeneous catalytic systems to help improve the efficiency and recyclability of the catalysts.

Covalent organic frameworks (COFs),^{9–11} an advanced class of crystalline porous polymers, have emerged as an excellent platform to address these issues due to their high chemical stability, tunable pore sizes, and high internal surface areas. These characteristics make COFs useful for applications related to gas storage,^{12,13} proton conduction,^{14,15} catalysis,^{16,17} optoelectronics,^{18,19} and energy storage.^{20–22} The modular nature of COFs permits the integration of suitable monomer units that can be metalated and utilized to complete any desirable catalytic transformation. For instance, Liu, Cui, and co-workers have shown²³ that salen-based two-dimen-

sional (2D) chiral COF systems metalated with Fe or Mn are effective at catalyzing the epoxidation of alkenes. Fang and co-workers have also demonstrated²⁴ that three-dimensional (3D) salphen-based COF systems metalated with Cu(II) are useful for removing superoxide radicals from antioxidants. While both of the systems highlight the utility of COFs as heterogeneous catalysts, examples of using COF-based systems to reductively cleave C–S bonds have not been reported.


Herein, we report the synthesis, characterization, and catalytic properties of an azine-linked 2D COF containing nickel-doped dehydrobenzoannulene (DBA)²⁵ units. DBAs are planar triangular-shaped macrocycles that have the ability to use their soft alkynyl ligands to form complexes with low oxidation state transition metals.^{26,27} However, to the best of our knowledge, the catalytic activity of metalated DBA complexes has not been reported. We demonstrate that the DBA[12] monomer units of DBA-COF 5 can be metalated with Ni(COD)₂ to generate Ni-DBA-2D-COF and used to reductively cleave the inert aryl C–S bonds of several organosulfur compounds using dimethylethylsilane as the reducing agent. Ni-DBA-2D-COF exhibits great recyclability with yields that are comparable to other Ni-based homogeneous catalytic systems.

DBA-COF 5 was synthesized by reacting DBA[12]-CHO with hydrazine in *o*-dichlorobenzene (*o*-DCB), *n*-butanol (*n*-BuOH), and 6 M acetic acid (AcOH) in a flame-sealed ampule at 120 °C for 72 h (Scheme 1). DBA-COF 5 was obtained by filtration and washed with methanol to produce a bright yellow crystalline powder. Thermogravimetric analysis revealed that

Received: January 27, 2020

Published: March 12, 2020

Scheme 1. Synthesis of DBA-COF-5 Using DBA[12]-CHO and Hydrazine Monomer Units Followed by Metalation with Ni(COD)₂ to Produce Ni-DBA-2D-COF

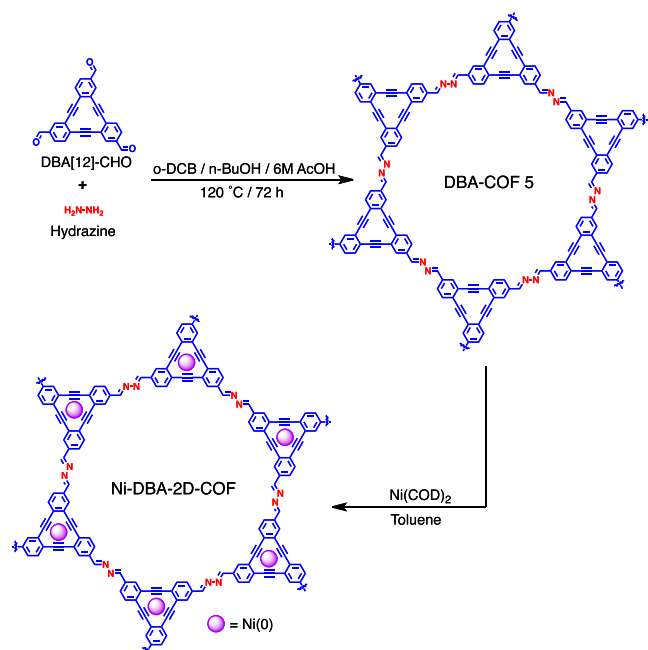

DBA-COF 5 maintains ~95% of its weight up to 430 °C (Figure S10, SI). Scanning electron microscopy (SEM) images revealed the formation of fluffy-like crystallites (Figure S11, SI). Metalation was achieved by combining 67 mg of DBA-COF 5 with 49 mg of Ni(COD)₂ in 6.5 mL of dry toluene. The mixture was then stirred at room temperature in an argon-purged glovebox for 16 h to produce Ni-DBA-2D-COF as a dark green crystalline powder. Ni-DBA-2D-COF was obtained by filtration and washed with dry hexanes to remove excess Ni(COD)₂. Inductively coupled plasma atomic emission spectroscopy (ICP-AES) analysis revealed that ~8.56 wt % of Ni was incorporated into Ni-DBA-2D-COF, which corresponds to ~64% of DBA[12] units being metalated.

The porosities of DBA-COF 5 and Ni-DBA-2D-COF were determined by nitrogen gas adsorption measurements at 77 K. DBA-COF 5 exhibited a type-I isotherm displaying a sharp uptake at low pressure ($P/P_0 < 0.1$), which is indicative of a microporous material (Figure 1). The Brunauer–Emmett–Teller (BET) model was applied over the low-pressure region ($0.03 < P/P_0 < 0.07$) of the isotherm to afford a surface area of 1643 m² g⁻¹. The total pore volume calculated at $P/P_0 = 0.899$ provided a value of 0.70 cm³ g⁻¹. The pore size distribution of DBA-COF 5 was estimated using the nonlocal density functional theory method (NLDFT), yielding an average pore size of 1.9 nm. The experimental pore size is lower than the theoretical value of 2.8 nm, which suggests that the adjacent layers are significantly offset. Ni-DBA-2D-COF also exhibited a type-I isotherm. Application of the BET model over the low-pressure region ($0.03 < P/P_0 < 0.07$) provided a surface area of 1565 m² g⁻¹. The NLDFT pore size of Ni-DBA-2D-COF revealed a slight reduction to 1.8 nm, which is very close to the experimental pore size of the DBA-COF 5. The total pore volume calculated at $P/P_0 = 0.899$ provided a value of 0.68 cm³ g⁻¹.

The crystallinities of DBA-COF 5 and Ni-DBA-2D-COF were evaluated using powder X-ray diffraction (PXRD).

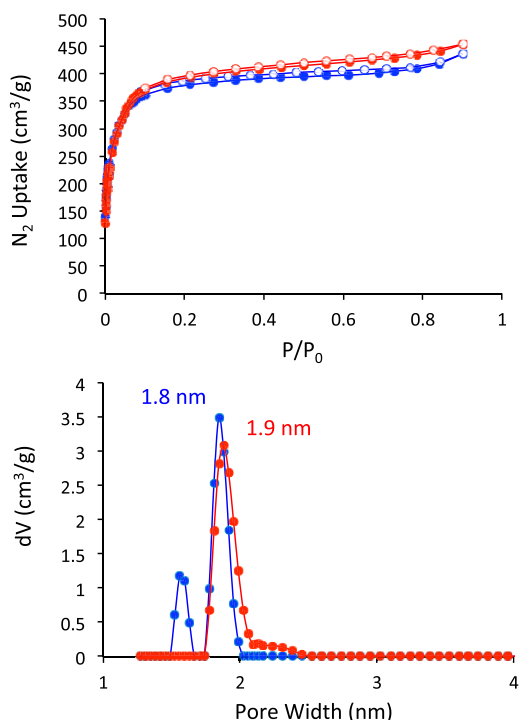


Figure 1. Nitrogen adsorption/desorption isotherms (top) and NLDFT pore size distributions (bottom) for DBA-COF 5 (red) and Ni-DBA-2D-COF (blue) measured at 77 K.

Considering the differences between the experimental and theoretical pore sizes, DBA-COF 5 was modeled using a P6 hexagonal unit cell in which the adjacent layers were offset by 9 Å (Figure 2). DBA-COF 5 exhibits an intense peak at 3.89° followed by smaller peaks at 6.73° and 26.5°, which correspond to the (100), (110), and (001) planes, respectively. Pawley refinement of the experimental data provided unit cell parameters of $a = b = 26.222$ Å and $c = 3.4$ Å (residuals $R_p = 3.81\%$, $R_{wp} = 5.12\%$). The simulated patterns were almost identical to the experimental plot. It should be noted that the

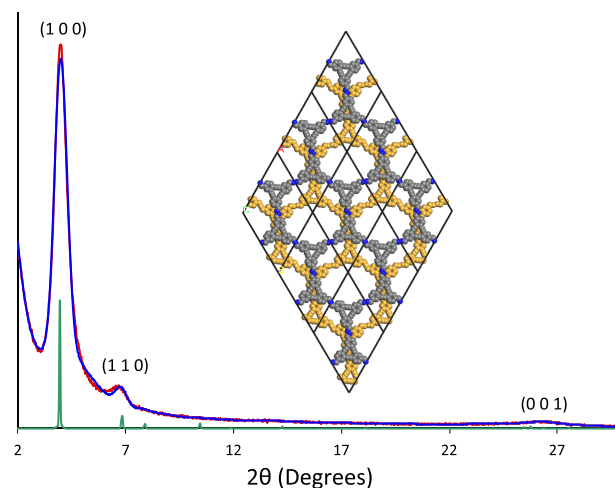


Figure 2. Indexed experimental (red) and Pawley refined (blue) PXRD patterns of DBA-COF 5 compared to the simulated hexagonal unit cell (green) with an offset of 9 Å and views along the x and y directions.

crystallinity of DBA-COF 5 is maintained after soaking the material in aqueous, acidic, and basic solutions for 24 h (Figure S5, SI). The PXRD profile of Ni-DBA-2D-COF also revealed retention of crystallinity following metalation with Ni(COD)₂ (Figure S4, SI). Surprisingly, Fourier transform infrared (FT-IR) spectra of DBA-COF 5 and Ni-DBA-2D-COF both exhibited identical $\text{C}\equiv\text{N}$ - and $\text{N}=\text{N}$ - stretching modes at 1620 and 1081 cm^{-1} , respectively, which suggests that the metal is predominantly bound within the cavity of DBA[12] to produce a Ni(0) 16-electron complex²⁸ with virtually no interaction at the azine linkage (Figure S1, SI).

The presence of the DBA-Ni(0) complex was confirmed by characterizing DBA-COF 5 and Ni-DBA-2D-COF using ¹³C cross-polarization magic angle spinning (CP-MAS) NMR and UV-vis diffuse reflectance spectroscopies. The alkynyl units for DBA-COF 5 were confirmed by ¹³C CP-MAS NMR displaying a distinct resonance at ~93 ppm (Figure S6, SI). After metalation, the alkynyl peak of DBA-COF 5 shifts downfield to ~109 ppm, which is indicative of forming the DBA-Ni(0) complex (Figure S7, SI).^{27,28} The UV-vis diffuse reflectance spectrum of DBA-COF 5 exhibits broad absorbance bands ranging from 200 to 500 nm (Figure 3). After

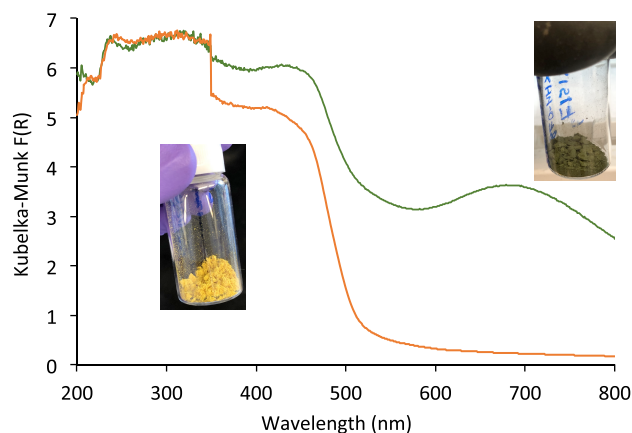


Figure 3. Kubelka–Munk diffuse reflectance spectra and photographs of DBA-COF 5 (orange) and Ni-DBA-2D-COF (green).

metalation, a noticeable charge transfer band surfaces at ~690 nm for Ni-DBA-2D-COF, which further suggests the formation of the DBA-Ni(0) complex. Lastly, the X-ray photoelectron spectroscopy (XPS) spectrum of Ni-DBA-2D-COF revealed the presence of two broad peaks at 855.89 and 852.89 eV, which correspond to the core energy levels of Ni(II)2p_{3/2} and Ni(0)2p_{3/2} (Figure S14, SI). The peak at 855.89 eV results from residual Ni(II) that is carried over after metalation with Ni(COD)₂.²⁸ XPS also confirmed the presence of the carbon, nitrogen, and oxygen atoms of Ni-DBA-2D-COF (Figure S13, SI).

Since the catalytic activity of metalated DBA complexes has not been experimentally evaluated or reported, we first assessed the reactivity of various aryl thioether substrates in the presence of dimethylethylsilane at temperatures ranging from 90 to 130 °C using 10 mol % Ni-DBA[12] (Scheme S1, SI) as a homogeneous catalyst (Table 1). Interestingly, the Ni-DBA[12] catalyst demonstrated great functional group tolerance and produced yields ranging from 26% to 99% for substrates 2a–2f. Substrate 2g produced the lowest yield (5%), which indicates that this system might not be capable of

Table 1. Catalytic Performance of Ni-DBA[12]^a and Ni-DBA-2D-COF^b for the Reductive Cleavage of Aryl C–S Bonds

Ni-DBA-2D-COF (10 mol%)
 or
Ni-DBA[12] (10 mol%)
 EtMe₂Si-H (5.0 equiv.)
 Toluene / 130 °C / 14 h

1a-h **2a-h**

Ni-DBA[12]	2a, 26% ^d	2b, 45%	2c, 99%	2d, 38% ^d
Ni-DBA-2D-COF	2a, 22% ^{c,d}	2b, 76% ^c	2c, 87% ^c	2d, 45% ^{c,d}
Ni-DBA[12]	2e, 79%	2f, 72%	2g, 5%	2h, 9%
Ni-DBA-2D-COF	2e, 46% ^c	2f, 44% ^c	2g, 2%	2h, 18% ^c

^aReaction conditions: 4.6 mg (0.011 mmol) of Ni-DBA[12] was added to 2.0 mL of toluene containing EtMe₂SiH (5 equiv, 0.55 mmol) and the aryl thioethers (0.11 mmol). ^bPerformed with 5.0 mg (0.011 mmol) of Ni-DBA-2D-COF. ^cYields are based on an average of three trials. ^dReaction was performed at 90 °C.

efficiently cleaving aryl substrates containing two thioether functionalities. Ni-DBA-2D-COF also exhibited a low yield for 2g, but much higher yields for 2a–2f (22–87%) and 2h (18%). It should be noted that these yields are higher than or comparable to other homogeneous Ni-based catalysts that have been utilized for the desulfurization of organosulfur compounds.^{6,29} Surprisingly, Ni-DBA-2D-COF exhibited excellent recyclability up to five cycles with no reduction in catalytic activity, providing yields ranging from 75% to 89% after reductively cleaving 2-(methylthio)naphthalene (1c) to produce 2c (Figure 4). XPS and PXRD data taken after

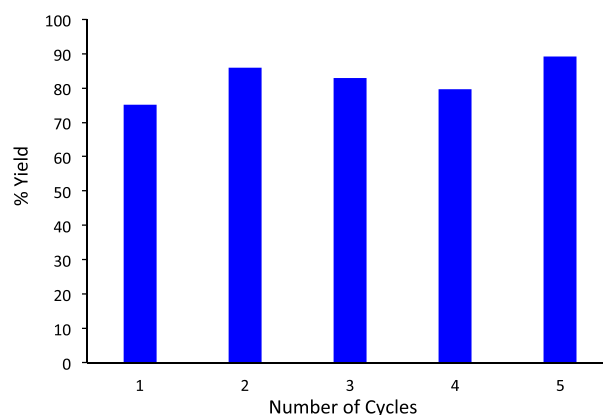


Figure 4. Recyclability of Ni-DBA-2D-COF after reductively cleaving 2-(methylthio)naphthalene (1c) at 130 °C using dimethylethylsilane as the reducing agent.

catalysis revealed preservation of the DBA-Ni(0) complex and retention of crystallinity, respectively (Figures S15 and S16, SI). The lack of additional peaks in the PXRD also suggests that no Ni-based nanoparticles are formed after catalysis. However, a nitrogen adsorption isotherm of Ni-DBA-2D-COF taken after catalysis revealed a slight reduction in the surface area of the material (Figures S17 and S18, SI). This reduction

could be attributed to minor amounts of desulfurized product trapped within the pores of Ni-DBA-2D-COF. In addition, a mercury poisoning experiment and leaching test confirmed that the heterogeneity of Ni-DBA-2D-COF remains intact (see Section N in the SI). ICP-MS analysis of the filtrate after catalysis also revealed minimal leaching of Ni ions ($\sim 0.02\%$).

Mechanistically, we believe that the DBA-Ni(0) catalytic system proceeds through a classical Ni(0)/Ni(II) catalytic pathway.³⁰ However, DFT calculations reveal that the aryl thioether substrates do not bind to the center of the DBA-Ni(0) complex due to the Ni center being coordinately saturated with all three alkynyl units (Figure S20, SI). As a consequence, the DFT calculations suggest that the Ni has to pop out of the DBA[12] cavity and bind with only one alkynyl unit to form a three-coordinate complex before it can oxidatively add into the C(aryl)–SMe bond. This initial oxidative addition step is estimated to be thermodynamically ~ 30 kcal/mol uphill, but accessible since the reaction is performed at high temperature. Afterward, σ -bond metathesis with dimethylethylsilane, followed by reductive elimination, regenerates the DBA-Ni(0) complex (Figure S23, SI). The σ -bond metathesis step is supported by the isolation and characterization of dimethylethyl(methylthio)silane, which is a common byproduct from this particular σ -bond metathesis reaction (Figure S22, SI).

In conclusion, we have demonstrated that a DBA-COF metalated with Ni can be used to reductively cleave inert aryl C–S bonds. The Ni-DBA-2D-COF catalytic system exhibited great recyclability and provided good yields. This work highlights a rare example of utilizing a Ni-doped DBA-COF as a platform for the desulfurization of organosulfur compounds. Since DBAs can be doped with other earth-abundant metals (i.e., Fe, Co, etc.),³¹ the proof-of-principle is important, as metalated DBA-COFs could also be utilized to perform many other sustainable catalytic transformations.

■ ASSOCIATED CONTENT

SI Supporting Information

The Supporting Information is available free of charge at <https://pubs.acs.org/doi/10.1021/jacs.0c01026>.

Synthetic procedures, FT-IR, solid-state ¹³C NMR, XPS, TGA PXRD, and SEM (PDF)

■ AUTHOR INFORMATION

Corresponding Author

Paras L. McGrier – Department of Chemistry and Biochemistry, The Ohio State University, Columbus, Ohio 43210, United States; [orcid.org/0000-0001-7637-4349](mailto:mcgrier.1@osu.edu); Email: mcgrier.1@osu.edu

Authors

W. Karl Haug – Department of Chemistry and Biochemistry, The Ohio State University, Columbus, Ohio 43210, United States

Eric R. Wolfson – Department of Chemistry and Biochemistry, The Ohio State University, Columbus, Ohio 43210, United States

Blake T. Morman – Department of Chemistry and Biochemistry, The Ohio State University, Columbus, Ohio 43210, United States

Christine M. Thomas – Department of Chemistry and Biochemistry, The Ohio State University, Columbus, Ohio 43210, United States

Complete contact information is available at: <https://pubs.acs.org/10.1021/jacs.0c01026>

Notes

The authors declare no competing financial interest.

■ ACKNOWLEDGMENTS

P.L.M. acknowledges financial support from the National Science Foundation (CHE-1856442). We thank The Ohio State University (OSU) Campus Chemical Instrument Center (CCIC) and Tanya Whitmer for assistance with the CP-MAS NMR measurements and access to the instrumentation. Electron microscopy was performed at the Center for Electron Microscopy and Analysis (CEMAS) at OSU. We also thank Dr. Yehia Khalifa for assistance with XPS measurements.

■ REFERENCES

- (1) Brunet, S.; Mey, D.; Pérot, G.; Bouchy, C.; Diehl, F. On the hydrodesulfurization of FCC gasoline: a review. *Appl. Catal., A* **2005**, *278*, 143–172.
- (2) Rentner, J.; Kljajic, M.; Offner, L.; Breinbauer, R. Recent advances and applications of desulfurization in organic synthesis. *Tetrahedron* **2014**, *70*, 8983–9027.
- (3) Huang, H.; Li, J.; Lescop, C.; Duan, Z. Palladium-Catalyzed Regioselective C–S Bond Cleavage of Thiophenes. *Org. Lett.* **2011**, *13*, 5252–5255.
- (4) Shibue, M.; Hirotsu, M.; Nishioka, T.; Kinoshita, I. Ruthenium and Rhodium Complexes with thiolate-Containing Pincer Ligands Produced by C–S Bond Cleavage of Pyridyl-Substituted Dibenzothiophenes. *Organometallics* **2008**, *27*, 4475–4483.
- (5) Vicić, D. A.; Jones, W. D. Modeling the Hydrodesulfurization Reaction at Nickel. Unusual Reactivity of Dibenzothiophenes Relative to Thiophene and Benzothiophene. *J. Am. Chem. Soc.* **1999**, *121*, 7606–7617.
- (6) Barbero, N.; Martin, R. Ligand-Free Ni-Catalyzed Reductive Cleavage of Inert Carbon–Sulfur Bonds. *Org. Lett.* **2012**, *14*, 796–799.
- (7) Mazingo, R.; Wolf, D. E.; Harris, S. A.; Folkers, K. Hydrogenolysis of Sulfur Compounds by Raney Nickel Catalyst. *J. Am. Chem. Soc.* **1943**, *65*, 1013–1016.
- (8) Hendsbee, J. A.; Thring, R. W.; Dick, D. G. Raney Nickel for the Desulphurization of FCC Gasoline. *J. Can. Petrol. Technol.* **2006**, *45*, 47–50.
- (9) Côté, A. P.; Benin, A. I.; Ockwig, N. W.; O’Keeffe, M.; Matzger, A. J.; Yaghi, O. M. *Science* **2005**, *310*, 1166–1170.
- (10) Huang, N.; Wang, P.; Jiang, D. Covalent organic frameworks: a materials platform for structural and functional designs. *Nat. Rev. Mater.* **2016**, *1*, 16068.
- (11) Bisbey, R. P.; Dichtel, W. R. Covalent Organic Frameworks as a Platform for Multidimensional Polymerization. *ACS Cent. Sci.* **2017**, *3*, 533–543.
- (12) Furukawa, H.; Yaghi, O. M. Storage of Hydrogen, Methane, and Carbon Dioxide in Highly porous Covalent Organic Frameworks for Clean Energy Applications. *J. Am. Chem. Soc.* **2009**, *131*, 8875–8883.
- (13) Zeng, Y.; Zou, R.; Zhao, Y. Covalent Organic Frameworks for CO₂ Capture. *Adv. Mater.* **2016**, *28*, 2855–2873.
- (14) Chandra, S.; Kundu, T.; Kandambeth, S.; Baba Rao, Y.; Marathe, S. M.; Kunjir, S. M.; Banerjee, R. Phosphoric Acid loaded Azo(–N = N–) Based Covalent Organic Framework for Proton Conduction. *J. Am. Chem. Soc.* **2014**, *136*, 6570–6573.
- (15) Xu, H.; Tao, S.; Jiang, D. Proton conduction in crystalline and porous covalent organic frameworks. *Nat. Mater.* **2016**, *15*, 722–726.

- (16) Ding, S.-Y.; Gao, J.; Wang, Q.; Zhang, Y.; Song, W.-G.; Su, C.-Y.; Wang, W. Construction of Covalent Organic Framework for Catalysis: Pd/COF-LZU1 in Suzuki-Miyaura Coupling Reaction. *J. Am. Chem. Soc.* **2011**, *133*, 19816–19822.
- (17) Fang, Q.; Gu, S.; Zheng, J.; Zhuang, Z.; Qiu, S.; Yan, Y. 3D Microporous Base-Functionalized Covalent Organic Frameworks for Size-Selective Catalysis. *Angew. Chem., Int. Ed.* **2014**, *53*, 2878–2882.
- (18) Dogru, M.; Handloser, M.; Auras, F.; Kunz, T.; Medina, D.; Hartschuh, A.; Knochel, P.; Bein, T. A. A Photoconductive Thienothiophene-Based Covalent Organic Framework Showing Charge Transfer Towards Included Fullerene. *Angew. Chem., Int. Ed.* **2013**, *52*, 2920–2924.
- (19) Duhović, S.; Dinca, M. Synthesis and Electrical Properties of Covalent Organic Frameworks with Heavy Chalcogens. *Chem. Mater.* **2015**, *27*, 5487–5490.
- (20) Mulzer, C.; Shen, L.; Bisbey, R. P.; McKone, J. R.; Zhang, N.; Abruña, H. D.; Dichtel, W. R. Superior Charge Storage and Power Density of a Conducting Polymer-Modified Covalent Organic Framework. *ACS Cent. Sci.* **2016**, *2*, 667–673.
- (21) Wolfson, E. R.; Xiao, N.; Schkeryantz, L.; Haug, W. K.; Wu, Y.; McGrier, P. L. A dehydrobenzoannulene-based two-dimensional covalent organic framework as an anode material for lithium-ion batteries. *Mol. Syst. Des. Eng.* **2020**, *5*, 97–101.
- (22) Vitaku, E.; Gannett, C. N.; Carpenter, K. L.; Shen, L.; Abruña, H. D.; Dichtel, W. R. Phenazine-Based Covalent Organic Framework Cathode Materials with High Energy and Power Densities. *J. Am. Chem. Soc.* **2020**, *142*, 16–20.
- (23) Han, X.; Xia, Q.; Huang, J.; Liu, Y.; Tan, C.; Cui, Y. Chiral Covalent Organic Frameworks with High Chemical Stability for Heterogeneous Asymmetric Catalysis. *J. Am. Chem. Soc.* **2017**, *139*, 8693–8697.
- (24) Yan, S.; Guan, X.; Li, H.; Li, D.; Xue, M.; Yan, Y.; Valtchev, V.; Qiu, S.; Fang, Q. Three-Dimensional Salphen-based Covalent-Organic Frameworks as Catalytic Antioxidants. *J. Am. Chem. Soc.* **2019**, *141*, 2920–2924.
- (25) Spitler, E. L.; Johnson, C. A., II; Haley, M. M. Renaissance of Annulene Chemistry. *Chem. Rev.* **2006**, *106*, 5344–5386.
- (26) Youngs, W. J.; Tessier, C. A.; Bradshaw, J. D. ortho-Arene Cyclynes, Related Heterocyclynes, and Their Metal Chemistry. *Chem. Rev.* **1999**, *99*, 3153–3180.
- (27) Baldwin, L. A.; Crowe, J. W.; Pyles, D. A.; McGrier, P. L. Metalation of a Mesoporous Three-Dimensional Covalent Organic Framework. *J. Am. Chem. Soc.* **2016**, *138*, 15134–15137.
- (28) Ferrara, J. D.; Tessier-Youngs, C.; Youngs, W. J. Synthesis and characterization of the first transition metal complex of 1,2:5,6:9,10-tribenzocyclododeca-1,5,9-triene-3,7,11-triyn. *J. Am. Chem. Soc.* **1985**, *107*, 6719–6721.
- (29) Eisch, J. J.; Hallenbeck, L. E.; Han, K. I. Desulfurization of Dibenzothiophene by Nickel(0) Complexes: Evidence for Electron Transfer in Oxidative Additions. *J. Org. Chem.* **1983**, *48*, 2963–296.
- (30) Fang, S.; Wang, M.; Liu, J.; Li, B.; Liu, J.-Y. Theoretical study on the reaction mechanism of “ligandless” Ni-catalyzed hydro-desulfurization of aryl sulfides. *RSC Adv.* **2017**, *7*, 51475–51484.
- (31) Srinivasu, K.; Ghosh, S. K. Transition Metal Decorated Graphyne: An Efficient Catalyst for Oxygen Reduction Reaction. *J. Phys. Chem. C* **2013**, *117*, 26021–26028.