

Bandgap Tuned 2D Boron Nitride/Tungsten Nitride Nanocomposites for Development of High-Performance Deep Ultra Violet Selective Photodetectors

Ali Aldalbahi^{1*}, Rafael Velázquez^{2#}, Andrew Zhou³, Mostafizur Rahaman¹ and Peter X. Feng^{2*}

¹Department of Chemistry, College of Science, King Saud University, Riyadh 11451, Saudi Arabia;

mrahaman@ksu.edu.sa (M.R.)

² Department of Physics, University of Puerto Rico, San Juan, PR 00936-8377, USA

³Department of Physics, Indiana University of Pennsylvania, Indiana, PA 15705, USA; fzhou@iup.edu (A.Z.)

* Correspondence: aaldalbahi@ksu.edu.sa (A.A.); peter.feng@upr.edu (P.X.F.); Tel.: +966-114-675-883

currently working at

Naval Air Warfare Center, Aircraft Division, Patuxent River, MD 20670

rafael.velazquez@navy.mil

Received: date; Accepted: date; Published: date

Abstract: This paper presents a fast and effective method to synthesize 2D boron nitride/tungsten nitride nanocomposites for tunable bandgap structure and devices. Few minutes of synthesis yields large numbers of high-quality 2D nanocomposites, with which a simple, low cost deep UV photo-detector (DUV-PD) was fabricated and tested. The new device was demonstrated to have very good performances. High responsivity up to 1.17 A/W, fast response time of lower than 2 ms, and highly stable repeatability have been obtained. Furthermore, influences of operating temperature, and applied bias voltage on the properties of DUV-PD as well as its band structure shift were investigated.

Keywords: 2D BN-WN nanocomposite; tunable bandgap; photodetector; fast response

1. Introduction

DUV radiation normally can be categorized into three distinct wavelength regions labeled as UVA, UVB and UVC. UVA covers the wavelengths from 400 to 315 nm, while UVB and UVC cover from 315 to 280 nm and from 280 to 100 nm, respectively. During the last several years, much progress has already been achieved on development of various visible-blind DUV-PD based on different wide band-gap (WBG) nanosemiconductors. Focus of WBG material research for these DUV-PDs was on oxide semiconductors [1–3], nitride semiconductors [4–7], silicon carbide [8,9], and nanodiamond [10,11] materials, as well as different nanocomposites [12,13]. Multilayer heterojunction structures were widely used [13], and they were basically classified into the metal-semiconductor-metal (MSM) structures, Schottky barriers, and p-i-n configurations [14,15]. Various criteria require consideration, including, among others, the optical wavelength of interest, semiconducting material composition and thicknesses, doping element and impurity concentration level, geometrical structures or architectures of devices, electrodes and interfaces.

Among differences, the MSM structures represent a simple, low-cost device design that are not only related to performance but also related to easy process in fabrication. The electrical current in MSM is mainly carried by majority charge carriers. The majority carrier current relies on the presence of the minority carriers. The minority carriers accumulate at one of the contacts, where they will cause additional injection of majority carriers until the minority carriers are recombined. It yields a large photoconductive gain. This is one of the important features for photoconductors. Normally, large bias

voltage is necessary for these PDs [16]. For example, Qian, et al. set the bias voltage to 20 V to operate Ga₂O₃ based photoconductor [17], and Jin, et al. developed ZnO based ultraviolet photoconductors operated at bias voltage of 50 V [18].

A challenge is that long carrier life times in MSM also cause slow response speeds. In the most cases, the reported response time was up to several ten seconds in rise and recovery times [18,19]. In this present work, we would report new results of MSM PDs based on emerging semiconductors. 2D boron nitride / tungsten nitride nanocomposites with controllable bandgap structures were utilized as a sensitive layer. The rationale is that tungsten nitride plays an important role in manipulating composite bandgap. It is closely related to the carrier density and carrier life times that directly affect device gain and response speed. Consequently, much short response time has been achieved. Due to the high responsivity to deep UV emission and insensitivity to sunlight, newly fabricated solar-blind photodetectors would possibly provide a wide range of applications, including ozone damage detection, jet engines related the missile, rocket monitoring and flame detection, combustion monitoring, chemical analysis, NASA space research and astronomy. Many of these applications require detectors capable of operating in high-temperature harsh environments. Relatively, Si and other narrow bandgap semiconductors are not able carry out those jobs.

2. Experimental Details

Good performance of DUV-PDs rely on their materials' properties and the detectors' structure design. The composite 2D BN-WN was fabricated by using a pulsed laser-produced plasma deposition technique. A complete explanation of this technique can be found in our previous paper [20]. In brief, a high-power CO₂ laser beam was focused onto BN target in a low (~80 mTorr) pressure chamber. The power density of laser beam on the target is around $\sim 10^8$ W/cm². Tungsten nitride was created using a thermal vapor technique. The BN and WN ratio was controlled at the 4.0 level. Si wafers with oxidized silicon surface as substrates were used and placed at 4 cm away from the target. The deposition temperature in substrate was around ~500 °C. Duration for deposition is 20 minutes. Then, a low temperature argon plasma source created at 200 mTorr pressure was utilized to treat nanocomposite layer for 20 minutes before fabrication of PD devices. The morphologies of nanocomposites were examined using a scanning electron microscopy (SEM) and a transmission electron microscopy (TEM). Physical properties were characterized with micro-Raman scattering spectroscopy. Finally, nanocomposite materials-based photodetectors were constructed and assessed.

It needs to be pointed out that a long minority carrier lifetime resulted in enhancement of photocurrent but also slowing the response speed. A basic trade-off involving the induced photocurrent strength and the response speed of a detector seems inevitable. Usually, the minority carrier time in doped material relies on the capture rate for holes and electrons at the recombination center. It is a function of the doping element concentration. Therefore, nanocomposite ingredient in the present work would be controlled in order to achieve a fast response time, while not to sacrifice too much in photocurrent gain. The obtained data clearly show that the nanocomposites minimized such trade-off and it displayed an anticipated balance for the DUV-PD's response speed and light-induced photocurrent strength.

3. Results and Discussion

3.1. Basic Characterization of Nanocomposite Materials

Figure 1(a) shows a SEM image of the nanocomposite prepared on wafer substrate. From the direct view, the obtained film has quite rough surface. The color of the sample appears grey and dull. SEM image of the composite shows it mainly consists of large numbers of small pieces uniformly distributing on entire substrate surface (1x2 cm²) area. With large magnification one could find that tiny pieces were related to nano sheets and nano ripples in random distributions as shown in Figure 1(b). Average size of

each continuous sheet is about a few square micrometer. Figure 1(c) shows TEM image of the nanocomposite film. Either sheets or particles were in nanoscale. Transparent property of sheets could be easily identified. EDS data indicate that the nanosheets were related to BN, and the nanoparticles were related to WN material.

In order to understand its good crystalline structures, a single sheet was picked up from the samples for HRTEM characterizations. Figure 1(d) shows its HRTEM image, from which it could be found that each atomic layer consists of a large amount of highly ordered boron and nitrogen atom arrays. The period is around 0.22 nm. B_3N_3 rings or two-dimensional benzene-like structures is clearly visible. Neither the N-N bond nor B-B bond was observed.

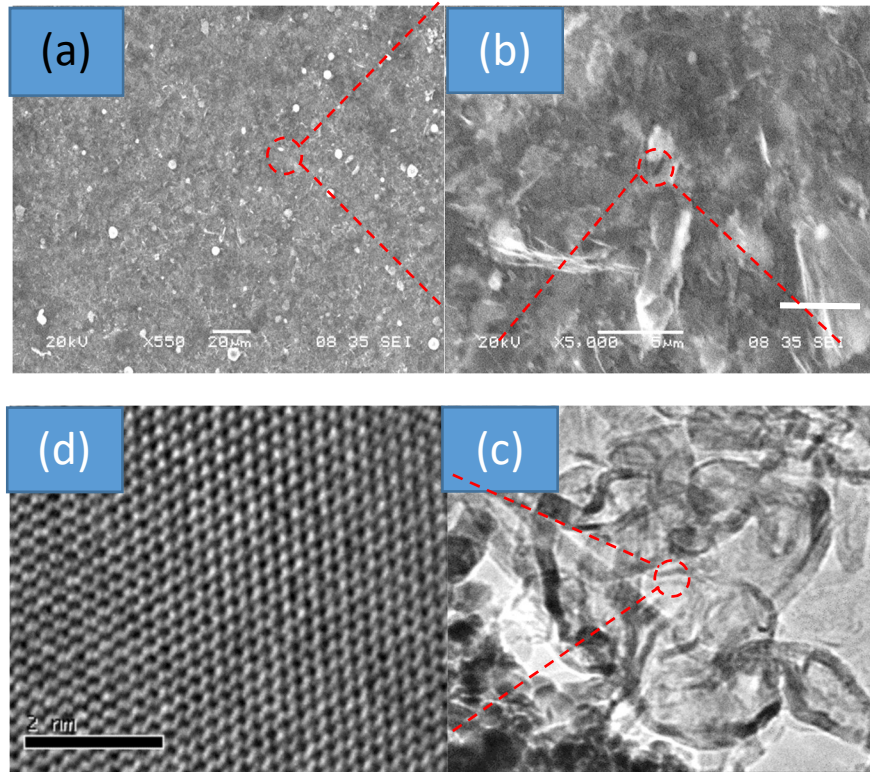


Figure 1. (a,b) SEM, (c) TEM, and d) HRTEM images of nanocomposite with different magnifications.

Raman spectroscopy was applied to evaluate the nanocomposites, and the results are showed in Figure 2a. The band situated at around $750\sim 850\text{ cm}^{-1}$ was assigned to W-N stretching models, whereas the band situated at around 250 cm^{-1} was attributed to W-N bending modes. The band at $200\sim 300\text{ cm}^{-1}$ has a stronger Raman signal than that one at $\sim 800\text{ cm}^{-1}$. This is different from that of WO [21–23]. In general, tungsten nitride forms together with little tungsten oxide. This is confirmed with EDS measurements. The oxygen is mainly from residue gas in the chamber during nanocomposites synthesis. Detailed discussion of spectral changes from WO to WO_xN_{1-x} and to WN can be found in previous work [24].

A Raman peak at 1355 cm^{-1} directly corresponds to the active E_{2g} mode of BN [7,25]. This narrow Raman spectral line suggests that the present deposition technique could yield high quality BN composites. Background noise was possibly because of a short accumulation time in Raman measurement. Either to choose higher laser power density or a slower sweep speed during sweeping wave number in Raman measurement would be helpful to obtain a better signal-to-noise ratio.

Three phenomena were observed from the magnified spectral line as shown in Figure 2b after comparing nanocomposite and binary BN Raman spectra. The first is that the Raman active E_{2g} mode with the hexagonal phase shifts from 1363 cm^{-1} for BN to 1355 cm^{-1} for BN-WN. The second is that the Raman spectral line of BN-WN appears to have a slightly asymmetric profile, and the third is that the

profile of Raman spectral line of nanocomposite is obviously broadened. These phenomena probably indicated existence of a little defect concentrations, or contamination. This is in good agreement with our previous results. Generally, the mechanism for the formation of crystalline BNNSs relies heavily on the selected method of synthesis. In the present case, laser heat-driven mechanical exfoliation dominates as the main process in the formation of high-quality crystalline BNNS. Nevertheless, appearance of intense, narrow hBN peak in Raman spectrum indicates the formation of high quality crystalline BN that dominates nanocomposite film.

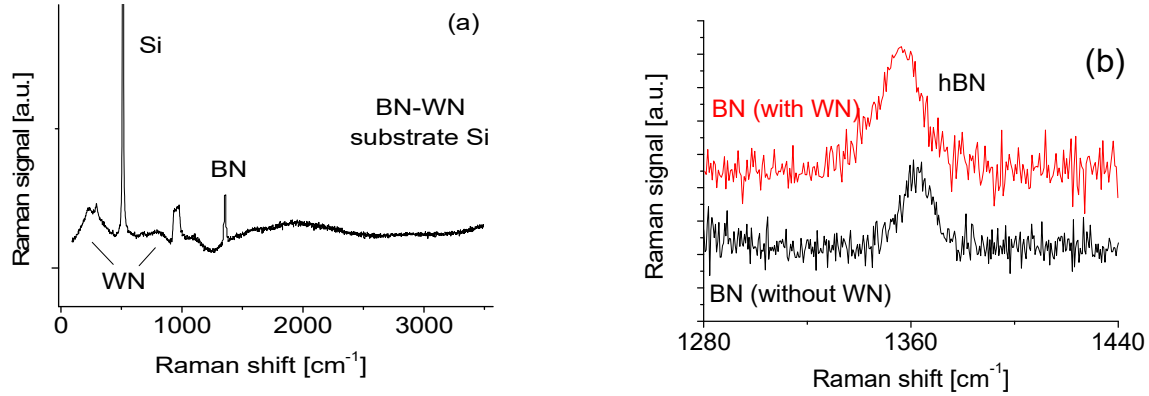


Figure 2. (a) Raman scattering spectrum of BN-WN nanocomposite, and (b) comparison of Raman spectra from BN-WN and BN materials.

3.2. Fabrication of BN-WN Based Prototype and Characterizations of its Basic Electrical Properties

In the present investigation, we extended our previous work on the use of binary BN semiconductor as sensing layer in PD by exploring, synthesis of emerging nanocomposites applied to MSM based DUV-PDs. The process flow of the prototype fabrication is detailed in Figure 3. Briefly, a low temperature argon plasma source was utilized to treat nanocomposite layer for 20 minutes. And then ~100 nm thick Cu electrodes were deposited at the two ends of the sensing layer. The space between the two Cu electrodes is 150 μm and the width of the same is 4 mm so that total exposed area is 0.6 mm². The sample was connected to a simple electric circuit to form a prototypic DUV PD for the detection of different deep UV radiations.

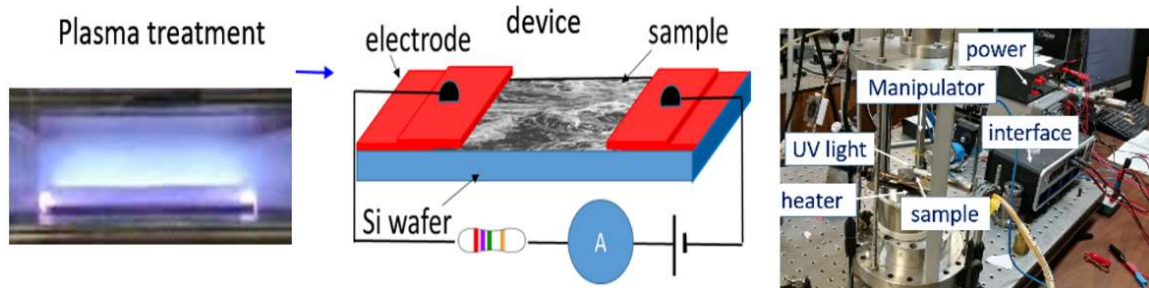


Figure 3. Process flow for nanocomposites based DUV-PD fabrication.

A planar structure of electrodes was employed in order to optimize the photo-electron collection near to the surface. The sensing layer consists of a large amount of BNNSs, and the thickness of the layer was around 3~5 μm obtained from cross section SEM image. No precise thickness can be obtained because BNNSs were heavily overlapped one another with random distributions, resulting a high roughness of the surface. This is very different from a solid thin film.

The current–voltage (I–V) properties at different operating temperatures were assessed at the homemade test station [26]. The measurements were performed under open-air atmospheric conditions. Figure 4a shows typical current–voltage properties of the prototype operating at 25, 80, 100 and 120 °C, respectively. Linear current–voltage curves are clearly visible, indicating it is a true Ohm contacts in the interface between the active layer and the electrodes in the prototype.

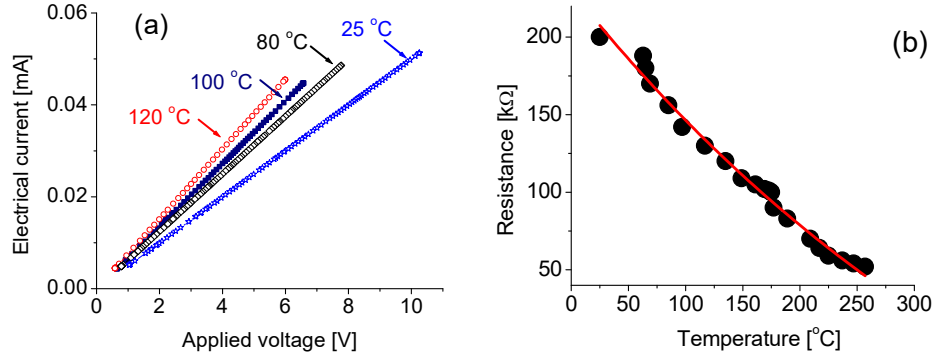


Figure 4. Current–voltage (I–V) properties of the DUV-PD.

Variations of temperature slightly affected the electrical properties. As seen in Figure 4b the resistance of nanocomposites varied from 200 kΩ, 160 kΩ, and 130 kΩ following temperature change from 25, 80 and 120 °C, respectively.

3.3. Bias Voltage Effect on Response to Light Radiation

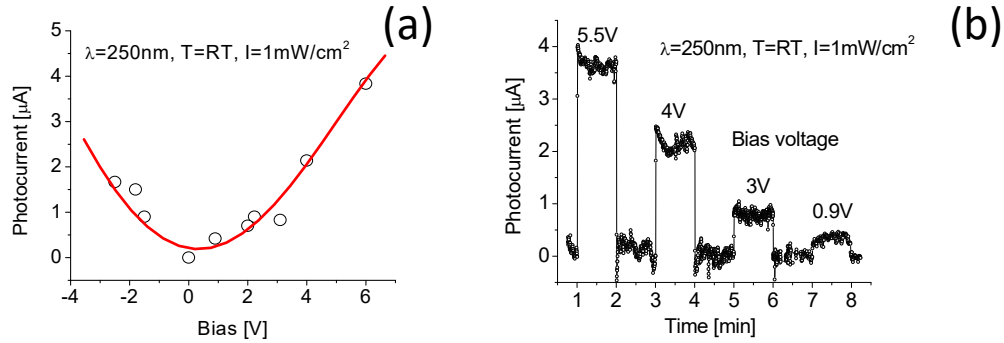


Figure 5. (a) The response of the DUV-PD as a function of the bias voltage magnitude, (b) time-dependent responses at different applied bias voltages with a fixed 250nm light radiation intensity and operating temperature.

Before characterization of spectral responses to light radiations, a bias voltage effect was evaluated. Figure 5a shows the induced photocurrent of nanocomposites based photodetector as a function of bias voltage where operating temperature and 250 nm radiation intensity remained unchanged. Figure 5b shows the corresponding time-dependent responses at selected biases. High bias voltage yields a high photocurrent or a large response rate (the ratio between the photocurrent output and the light radiation power input). As seen from Figure 5, the induced photocurrent at bias voltage of 5.5 V is about 9 times as large as that at bias voltage of 0.9 V. At the same bias voltage magnitude, the light induced photocurrent under the forward bias voltage is nearly the same value as that under the reverse bias voltage. This is directly attributed to the fact that the prototypic DUV-PD has a MSM structure. The MSM structures

represents a simple, low-cost device design. The electrical current in MSM is mainly carried by majority charge carriers. The majority carrier current relies on the presence of the minority carriers. The minority carriers accumulate at one of the contacts, where they would cause additional injection of majority carriers until the minority carriers are recombined. It yields a large photoconductive gain. This is one of the important features for MSM photoconductors. Their main limitations include relatively large dark current (since a bias voltage is required). Therefore, signal-to-noise ratio is relatively low.

A slight variation of the stabilities in response signals and baselines were observed at a high bias voltage as detailed in Figure 5b. It is expected that the increase of bias voltage magnitude would unavoidably cause a large dark current or noise. Therefore, a slightly low bias voltage would always be applied in the following experiments.

3.4. Spectral Responses to UV Radiations

Cyclic tests were carried out to understand how reliable or repeatable newly fabricated photodetector is. Figure 6 shows the spectral responses of the device during cyclic tests. Good repeatability and stable baseline features were clearly visible. When the cyclic tests with 250 nm radiation, the light induced photocurrent rises rapidly at initial period, and then reaches its maximum. Once the radiation source was turned off, the photocurrent quickly dropped. The induced photocurrent was directly associated to deep ultraviolet light absorption. The maximal photocurrent obtained is 0.84 μA . Because the exposed area of the PD is $\sim 0.6 \text{ mm}^2$ and the 250 nm radiation power on the active layer is 6 μW , the estimated responsivity (yielded photocurrent to radiation power on the PD) of the PD is around 140 mA/W. This value is more than 100 times larger than that previously reported results obtained either from 2D BN nano sheets based or from oxide semiconductor based Schottky deep UV photodetectors [27–29].

Decreasing the 250 nm UV radiation intensity down to 0.3 mW/cm² on the active layer, the induced photocurrent of the PD drops to 0.53 μA . Further decreasing the 250 nm light radiation intensity to 0.1 mW/cm², the generated photocurrent drops to 0.34 μA . Consequently, a large responsivity up to 560 mA/W was obtained. The phenomenon related to a relatively small value (140 mA/W) of the responsivity at intense (1mW/cm²) deep UV light illumination is possibly due to the saturation effect in light absorption. Such phenomenon was also found in our previous experiments [25].

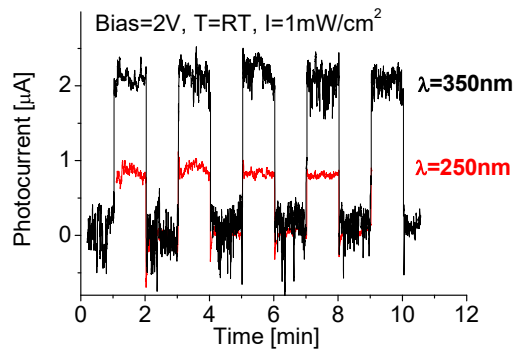


Figure 6. Responses of the device during cyclic tests with 2 minutes period at RT exposed to 250nm, and 350 nm UV radiations. RT: room temperature; λ : wavelength ; B: bias voltage.

Interestingly, the fabricated device appears to have the highest response signal to 350 nm light radiation. It is known that the spectral response for the binary BN based prototypes in the wavelengths ranging from 185 nm to 550 nm has a peak at around 200~250nm [25]. The red spectral shift for BN-WN is due to intrinsic behavior of the nanocomposite, as well as its complex, multifactor nature. The best way

for measurement of the bandgap shift is to use spectrometers. As an option, Mendoza's model could also be used [30], with which it was found that the bandgap of the binary BN nanomaterial is around 5 eV (~250 nm), whereas the nanocomposite has a bandgap shift down to 3.5 eV. As seen that 1mW/cm² 350 nm radiation yielded an induced photocurrent up to 2.2 μ A. This is almost 2.6 times as large as that exposed to 250 nm radiation at the same intensity. As radiation intensities decrease from 1.0 to 0.3, and to 0.1 mW/cm², the induced photocurrent decreases from 2.2, 1.4, and 0.7 μ A, accordingly, the obtained responsivity is 0.33, 0.78, and 1.17 A/W, respectively.

As seen that a large photoconductive gain is a very important feature for MSM photoconductor. The obtained high value of responsivity could also be attributed to a synergistic effect because the nanocomposite material BN-WN was used. This is very different from previous work where most were constructed solely from one material. Composites or multistructures based materials showed significantly higher efficiency than conventional prototypes constructed solely from one material when tested under identical experimental conditions, suggesting a synergistic effect between the two components.

3.5. Time Response

In order to analysis response time, a high-resolution interface was utilized to measure the time response of the nanocomposite based DUV-PD. Typical results are shown in Figure 7, from which the response and recovery times were estimated around 2 ms.

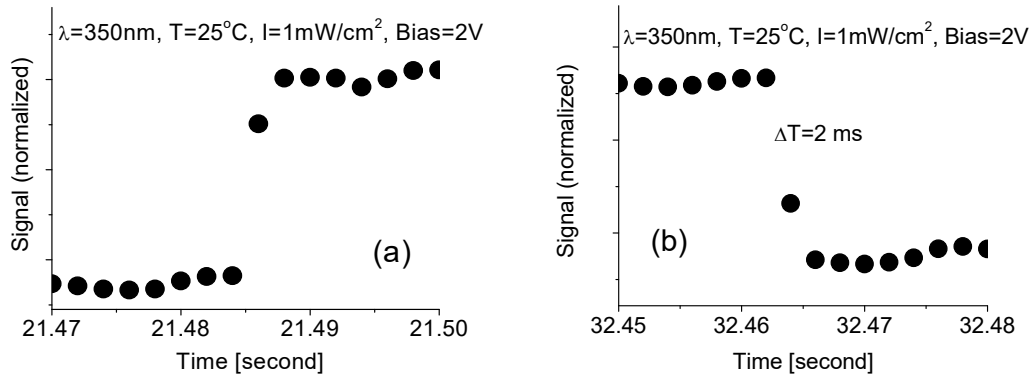


Figure 7. The time response of the DUV-PD exposed to 350nm light radiation at intensity of 1 mW/cm², room temperature, and 2 V bias voltage.

The theoretical limit for the photodetector speed depends on the transit time of electrons and holes in the device, the carrier diffusion and the carrier multiplication process in the BN-WN, as well as the circuit time constant. The present prototype should have a fast response speed. This is because the improvement of BN-WN in crystalline quality reduces the recombination and then reduces the response time. Therefore, it can be expected that the real response and recovery times of DUV-PD are shorter than they appears. This is because of the delay in reaching the full intensity after turning on the UV lamp, and residual photo-luminescence of the UV light source. The best way for precise measurement of response time is to use a pulsed DUV laser beam or an aligned DUV light beam with an optical chopper System. Unfortunately, this equipment is not available in our laboratories.

3.6. Temperature Effect

It was found that variation in operating temperature significantly affected performance of the prototype exposed to 300 nm radiation as shown in Figure 8. At 25 $^\circ\text{C}$, either response time or recovery

time was around few milliseconds. Once the temperature increased to 150 °C, the response time remained nearly unchanged but the recovery time became longer, around few hundred milliseconds. It is also clear that high operating temperature would result in an intense noise signal, and relatively low induced photocurrent. In other words, the obtained photocurrent drops from 0.9 to 0.5 μA following operating temperature increase from room temperature to 150 °C.

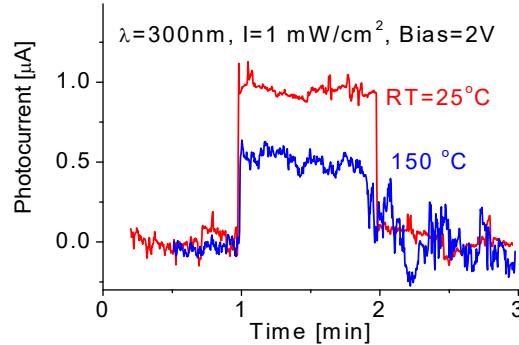


Figure 8. Thermal effect on the responses of the prototypic DUV-PD to 1 mW/cm².

Similar phenomenon was also found from the DUV-PD exposed to 250 nm UV radiation, where the response signal or induced photocurrent drops from 0.84 to 0.24 μA following temperature increase from room temperature to 150 °C. From these experimental data above we could conclude that even though operating temperature was up to 150 °C, the prototype still ran well with stable repeatability.

4. Conclusions

Even though syntheses of nanocomposite materials are extremely easy, and fabrication of this prototype is simple and cost effective, experiments demonstrated that the newly designed prototype has very good performances including fast response time, high photocurrent, good baseline stability, and repeatability. Maximal responsivity up 1.17 A/W, and response time lower than 2 ms have been achieved. Bandgap shift associated to nanocomposite ingredients directly affects selective spectral responses.

It was concluded that operating temperature would notably affect the performance of BN-WN composite based DUV-PD. When the temperature increases to 150 °C, the induced photocurrent would decrease down to 30 %. The recovery time becomes a slightly longer but the response time remains unchanged and the prototype still works well with clear response signal and good responsivity.

Author Contributions: All authors work together on designing and performing the experiments, as well as analyzing the data and writing the manuscript.

Acknowledgments: This work is financially supported by NSF-CREST Center for Innovation, Research and Education in Environmental Nanotechnology (CIRE2N) Grant Number HRD-1736093. The authors acknowledge King Saud University, Riyadh, Saudi Arabia, for funding this work through Researchers Supporting Project number (RSP-2020/30).

Conflicts of Interest: The authors declare no conflict of interest.

References

1. Alenezi, M.R.; Henley, S.J.; Silva, S.R.P. On-chip fabrication of high performance nanostructured ZnO UV detectors. *Sci. Rep.* **2015**, *5*, 8516.
2. Agrawal, J.; Dixit, T.; Palani, I.A.; Singh, V. Systematic investigations on the effect of prolong UV illumination on optoelectronic properties of ZnO honeycomb nanostructures. *Scripta Materialia* **2019**, *163*, 1.

3. Liu, Z.; Li, F.; Li, S.; Hu, C.; Wang, W.; Wang, F.; Lin, F.; Wang, H. Fabrication of UV photodetector on TiO₂/diamond film. *Sci. Rep.* **2015**, *5*, 14420.
4. Velazquez, R.; Aldalbahi, A.; Rivera, M.; Feng, P. Fabrications and application of single crystalline GaN for high-performance DUV photodetectors. *AIP Adv.* **2016**, *6*, 85117.
5. Dahal, R.; Li, J.; Majety, S.; Pantha, B.N.; Cao, X.K.; Lin, J.Y.; Jiang, H.X. Epitaxially grown semiconducting hexagonal boron nitride as a deep ultraviolet photonic material. *Appl. Phys. Lett.* **2011**, *98*, 211110.
6. Laksana, C.; Chen, M.R.; Liang, Y.; Tzou, A.J.; Kao, H.L.; Jeng, E.; Chen, J.; Chen, H.G.; Jian, S.R. Deep-UV sensors based on SAW oscillators using low-temperature-grown AlN films on sapphires. *IEEE Trans. Ultrason. Ferroelectr. Freq. Control.* **2011**, *58*, 1688.
7. Rivera, M.; Velázquez, R.; Aldalbahi, A.; Zhou, A.F.; Feng, P.X. UV photodetector based on energy bandgap shifted hexagonal boron nitride nanosheets for high-temperature environments. *J. Phys. D: Appl. Phys.* **2018**, *51*, 045102.
8. Aldalbahi, A.; Li, E.; Rivera, M.; Velazquez, R.; Altalhi, T.; Peng, X.; Feng, P.X. A new approach for fabrications of SiC based photodetectors. *Sci. Rep.* **2016**, *6*, 23457.
9. Toda, T.; Hata, M.; Nomura, Y.; Ueda, Y.; Sawada, M.; Shono, M. Operation at 700°C of 6H-SiC UV Sensor Fabricated Using N⁺ Implantation. *Japanese J. Appl. Phys. Part 2 Lett.* **2004**, *43*, 9.
10. Lin, C.R.; Wei, D.H.; BenDao, M.K.; Chen, W.E.; Liu, T.Y. Development of High-Performance UV Detector Using Nanocrystalline Diamond Thin Film. *Int. J. Photoenergy* **2014**, *2014*, 1–8.
11. Pace, E.; De Sio, A. Innovative diamond photo-detectors for UV astrophysics. *Mem. S. A. It. Suppl.* **2010**, *14*, 84.
12. Hou, M.; So, H.; Suria, A.J.; Yalamarthy, A.S.; Senesky, D.G. Suppression of persistent photoconductivity in AlGaIn/GaN ultraviolet photodetectors using in situ heating. *IEEE Electron Device Lett.* **2017**, *38*, 56.
13. Moustakas T.D.; Paiella, R. Optoelectronic device physics and technology of nitride semiconductors from the UV to the terahertz. *Rep. Prog. Phys.* **2017**, *80*, 106501.
14. Aldalbahi, A.; Zhou, A.F.; Tan, S.; Feng, P. Fabrication, Characterization and Application of 2D Boron Nitride Nanosheets Prepared by Pulsed Laser Plasma Deposition. *Rev. Nanosci. Nanotechnol.* **2016**, *5*, 79.
15. BenMoussa, A.; Soltani, A.; Schühle, U.; Haenen, K.; Chong, Y.M.; Zhang, J.; Dahal, R.; Lin, J.Y.; Jiang, H.X.; Barkad, H.A.; BenMoussa, B.; Bolsee, D.; Hermans, C.; Kroth, U.; Laubis, C.; Mortet, V.; De Jaeger, J.C.; Giordanengo, B.; Richter, M.; Scholze, F.; Hochedez, J.F. Recent developments of wide-bandgap semiconductor based UV sensors. *Diam. Relat. Mater.* **2009**, *18*, 860.
16. Lee, S.H.; Kim, S.B.; Moon, Y.J.; Kim, S.M.; Jung, H.J.; Seo, M.S.; Lee, K.M.; Kim, S.K.; Lee, S.W. High-Responsivity Deep-Ultraviolet-Selective Photodetectors Using Ultrathin Gallium Oxide Films. *ACS Photonics* **2017**, *4*, 2937.
17. Qian, L.X.; Wang, Y.; Wu, Z.H.; Sheng, T.; Liu, X.Z. β -Ga₂O₃ solar-blind deep-ultraviolet photodetector based on annealed sapphire substrate. *Vacuum* **2017**, *140*, 106.
18. Jin, Z.; Gao, L.; Zhou Q.; Wang, J. High-performance flexible ultraviolet photoconductors based on solution-processed ultrathin ZnO/Au nanoparticle composite films. *Sci. Rep.* **2014**, *4*, 4268.
19. Wu, Z.; Bai, G.; Qu, Y.; Guo, D.; Li, L.; Li, P.; Hao, J.; Tang, W. Deep ultraviolet photoconductive and near-infrared luminescence properties of Er doped β -Ga₂O₃ thin films. *Appl. Phys. Lett.* **2016**, *108*, 211903.
20. Sajjad, M.; Peng, X.Y.; Chu, J.; Zhang, H.X.; Feng, P.X. Design and Installation of CO₂-pulsed laser plasma deposition system for the synthesis of mass product nanostructures. *J. Mater. Res.* **2013**, *28*, 1747.
21. Feng, P.X.; Wang, X.P.; Zhang, H.X.; Yang, B.Q.; Wang, Z.B.; González, A.; Morell, G.; Weiner, B. Study of the structural evolutions of the crystalline tungsten oxide films prepared using hot-filament CVD. *J. Phys. D: Appl. Phys.* **2007**, *40*, 5239.
22. Zhang, H.X.; Yang, B.Q.; Feng, P.X. Ambient Pressure Synthesis of Nanostructured Tungsten Oxide Crystalline Films. *J. Nanomater.* **2008**, *2008*, 957935.
23. FengChen, S.; Aldalbahi, A.; Feng, P. Nanostructured tungsten oxide composite for high-performance gas. *Sensors* **2015**, *15*, 27035-27046.
24. Mohamed, S.H.; Anders, A. Structural, optical and electrical properties of WO_xNy films deposited by reactive dual magnetron sputtering. *Surf. Coat. Technol.* **2006**, *201*, 2977.
25. Aldalbahi, A.; Rivera, M.; Rahaman, M.; Zhou, A.F.; Mohammed, A.W.; Feng, P. High-performance and self-powered deep UV photodetectors based on high quality 2D boron nitride nanosheets. *Nanomaterials* **2017**, *7*, 454.
26. Feng, P.; Aldalbahi, A. A compact design of a characterization station for far UV photodetectors. *Rev. Sci. Instrum.* **2018**, *89*, 015001.

27. Rivera, M.; Velázquez, R.; Aldalbahi, A.; Zhou, A.F.; Feng, P. High Operating Temperature and Low Power Consumption Boron Nitride Nanosheets Based Broadband UV Photodetector. *Sci. Rep.* **2017**, *7*, 42973.
28. Zhou, A.F.; Aldalbahi, A.; Feng, P. Vertical metal-semiconductor-metal deep UV photodetectors based on hexagonal boron nitride nanosheets prepared by laser plasma deposition. *Opt. Mater. Exp.* **2016**, *6*, 3286.
29. Chen, X.; Liu, K.; Zhang, Z.; Wang, C.; Li, B.; Zhao, H.; Zhao, D.; Shen, D. Self-Powered Solar-Blind Photodetector with Fast Response Based on Au/ β -Ga₂O₃ Nanowires Array Film Schottky Junction. *ACS Appl. Mater. Interfaces* **2016**, *8*, 4185.
30. Mendoza, F.; Makarov, V.; Hildalgo, A.; Weiner, B.; Morell, G. Ultraviolet Photosensitivity of Sulfur-Doped Micro- and Nano-Crystalline Diamond. *J. Appl. Phys.* **2011**, *109*, 114904.