

ARTICLE

Effect of metallocupramolecular polymer concentration on the synthesis of poly[n]catenanes†

Marissa M. Tranquilli,^a Qiong Wu,^b Stuart J. Rowan^{a,b,c}Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

Poly[n]catenanes are a class of polymers that are composed entirely of interlocked rings. One synthetic route to these polymers involves the formation of a metallocupramolecular polymer (MSP) that consists of alternating units of macrocyclic and linear thread components. Ring closure of the thread components has been shown to yield a mixture of cyclic, linear, and branched poly[n]catenanes. Reported herein are investigations into this synthetic methodology, with a focus on a more detailed understanding of the crude product distribution and investigations into how the concentration of the MSP during the ring closing reaction impacts the resulting poly[n]catenanes. In addition to a better understanding of the molecular products obtained in these reactions, the results show that the concentration of the reaction can be used to tune the size and type of poly[n]catenanes accessed. At low concentrations the interlocked product distribution is limited to primarily oligomeric and small cyclic catenanes (number average molar mass $\overline{M}_n = 6.2$ kg/mol, number of rings = 4). However, the same reaction at increased concentration can yield branched poly[n]catenanes with an $\overline{M}_n$ ca. 21 kg/mol and evidence of structures with as many as 640 interlocked rings (1000 kg/mol).

Introduction

Catenated compounds—molecules composed of interlocked rings—have been of interest since the mid 20th century when they were first synthesized.^{1,2} The interlocked rings are held together by what is termed the mechanical bond, which is a bonding motif that offers a unique combination of flexibility and strength.^{3–5} A covalent bond must be broken in order to separate the two components; however, the mechanically bonded nature of the rings allow the components to twist, rotate, and expand/contract relative to each other, offering

modes of motion that are not possible with molecules comprised of only covalent bonds (Figure 1).

It is therefore perhaps not surprising that the incorporation of the mobile mechanical bond into polymer architectures has been an active area of research since the early days of the field.⁶ As more efficient synthetic methods have been developed to access interlocked molecules, there has been a corresponding growth of activity into mechanically interlocked polymers (MIPs).^{7–10} These new polymeric materials exhibit unusual property profiles,¹¹ that include increased stress dissipation and high extensibility.^{12–14} One of the more intriguing MIP architectures is the poly[n]catenane—a polymer chain that is entirely comprised of interlocked macrocycles where the number of mechanical bonds is optimized (Figure 1). Molecular simulations of these poly[n]catenanes have begun to outline the unique dynamic and rheological properties they possess.¹⁵ In solution, modelling shows that a single poly[n]catenane chain demonstrates dynamics qualitatively similar to those found in entangled polymer melts, yet such effects are observed at shorter time scales, suggesting these polymers will demonstrate unique rheological and dynamical responses.¹⁶ Similarly, modelling of these polymers in the melt has shown several phenomena including fast stress relaxation and unusual viscosity trends.¹⁷

While networks of catenanes (so-called Olympic networks) occur naturally in the DNA of some protozoic organisms,^{18–20} the laboratory synthesis of polymeric catenanes composed of only interlocked rings has long been a challenge.⁷ Early examples of (oligo)[n]catenanes include the step-wise synthesis of linear [5]catenanes (Olympiadane) and branched [7]catenanes.^{21–23} Other promising methodologies, such as ring merging²⁴ or ring-opening of a [2]catenane²⁵ have been investigated. While both

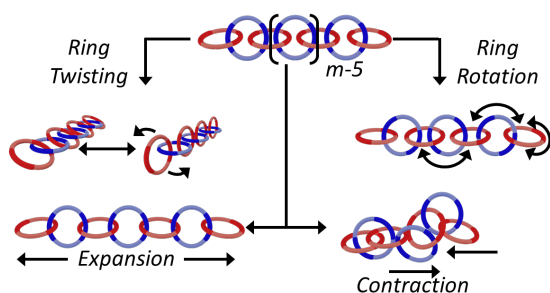


Fig. 1 A poly[n]catenane consists of n interlocked rings held together by the mechanical bond which imparts unique mobility elements to the polymer, such as ring twisting and rotation and chain collapse/expansion.

^a Department of Chemistry, University of Chicago, Chicago, IL, USA

^b Pritzker School of Molecular Engineering, University of Chicago, Chicago, IL, USA.
Email: stuartrowan@uchicago.edu

^c Chemical and Engineering Sciences, Argonne National Laboratory, Lemont, IL, USA

† Electronic Supplementary Information (ESI) available: Novel experimental procedures, ¹H NMR spectra, DOSY NMR Analysis, NMR analysis calculations, GPC MALS deconvolution and MALS analysis, chain end analysis calculation.

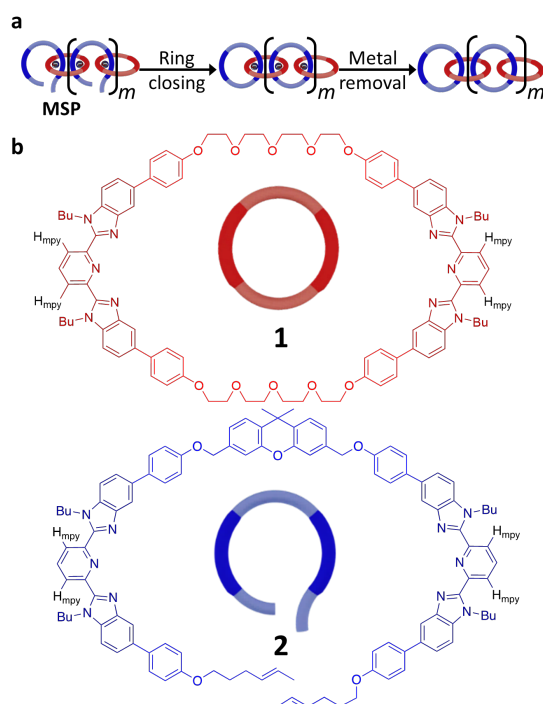


Fig. 2 (a) Poly[*n*]catenanes can be synthesized by assembly of a ditopic thread-like component (blue) and a ditopic macrocycle (red) via metal-templating to yield a metallosupramolecular polymer (MSP). Ring closure of the blue component within the MSP followed by demetallation yields the poly[*n*]catenane. (b) Chemical structures and cartoon representations of the macrocyclic (**1**) and thread (**2**) components used in the synthesis of the poly[*n*]catenane. The 2,6-bisbenzimidazolylpyridine (Bip) component is darkened for identification and the *m*-pyridyl protons (H_{mpy}) are indicated in black.

are attractive synthetic routes, high molecular weight poly[*n*]catenanes structures have yet to be reported with such approaches. However, it is worth mentioning that the formation of Olympic networks has been proposed as a by-product in the polymerization of 1,2-dithianes.^{26,27}

The synthesis of high molecular weight poly[*n*]catenanes^{7,28,29} is challenging, as catenane synthesis requires a ring closing step that is notoriously low yielding.⁷ A common approach to low molecular weight catenanes, pioneered by Sauvage, involves the threading of a linear component (or thread) through a pre-made ring driven by metal-ligand coordination,^{30–33} followed by ring closing of the thread under dilute conditions.³⁴ Recently, this metal-templated approach has been expanded³⁵ to allow access to poly[*n*]catenanes via the self-assembly of ditopic macrocyclic and thread components with a metal ion to form a metallosupramolecular polymer (MSP), followed by the ring closing reaction of the thread component and demetallation (Figure 2a). A 1:1 solution of macrocycle (**1**) and thread (**2**), which both contain two 2,6-bisbenzimidazolylpyridine (Bip) ligands (Figure 2b), were mixed with two equivalents of Zn^{2+} ions to yield the pseudopolyrotaxane MSP (**3**) (Figure 3). Ring closing of **2** was achieved through olefin metathesis of its alkene tails at a concentration of 2.5 mM (wrt. **2**) resulting in a mixture that contains the metallated catenane (**4**). Ideally, the alkene tails of **2** react intramolecularly to undergo a ring closing metathesis reaction, yielding the desired poly[*n*]catenanes (**5a**) after demetallation. However, studies on the demetallated products showed that in addition to the targeted linear poly[*n*]catenane (**5a**) the reaction mixture also contained cyclic and branched catenated products (**5b/c**) as well as the starting materials (**1**, **2**). In addition, non-interlocked by-products derived from **2**, namely macrocycle **7** (formed by ring closing of **2**) and oligomer **6**, formed via the Acyclic Diene Metathesis

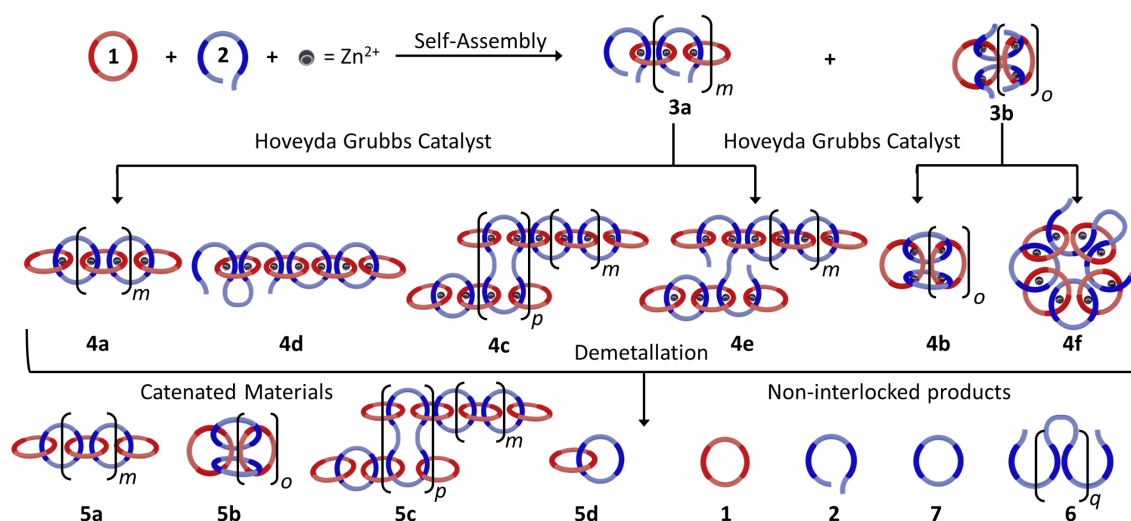


Fig. 3 Mixing macrocycle (**1**) and thread (**2**) in a 1:1:2 ratio with zinc di[bis(trifluoromethylsulfonyl)imide] [$Zn(Tf_2N)_2$] results in the self-assembly of linear (**3a**) and/or cyclic (**3b**) metallosupramolecular polymers (MSP). Subsequent reaction of the MSP with Hoveyda Grubbs catalyst can yield a mixture of metallated products (some of which are shown as **4a-f**) whose distribution depends on the nature of the MSP and concentration of the reaction. Demetallation of these reaction products yields poly/oligo[*n*]catenanes (e.g., **5a-d**) along with recovery of some starting material and some non-interlocked byproducts.

(ADMET) of **2** (which can be formed either via incorrect intramolecular MSP reactions, as in **4d**, or intermolecular MSP reactions, as in **4e**). Through a combination of NMR and GPC-MALS (gel permeation chromatography coupled to a multi-angle light scattering detector) studies, it was shown that the overall yield of the interlocked compounds was ca. 75% and, after some purification to remove the non-interlocked products (along with a small amount of low molecular weight interlocked oligomers), the poly[*n*]catenanes were obtained with a number average molar mass ($\overline{M}_n$) of 21.4 kDa ($\overline{DP} = 14$) (note $\overline{DP}$ as it is calculated here, Eq. S1, is the average number of rings in the polymer). Fractionation of this product allow confirmation that it consisted of a mixture of linear (**5a**), cyclic (**5b**), and branched (**5c**) poly[*n*]catenanes (Figure 3). It was suggested that the cyclic poly[*n*]catenanes are formed from a cyclic MSP template (**3b**) while the branched poly[*n*]catenanes result from inter-MSP reactions.

This prior study focused primarily on confirming the synthesis of poly[*n*]catenanes. As such, the reaction was primarily studied at a single concentration (2.5 mM wrt. **2**) and no detailed characterization of the crude product distribution was undertaken. It is reasonable to expect that both the MSP assembly and the ring closing olefin metathesis reaction will be sensitive to monomer concentration. Thus, the goal of this work is to build on these prior observations by carrying out the ring closing reactions across a range of monomer concentrations (0.25 – 10 mM) and analyzing the crude reaction mixtures (after demetallation) to obtain a better understanding of how different reaction conditions impact this synthetic route to poly[*n*]catenanes.

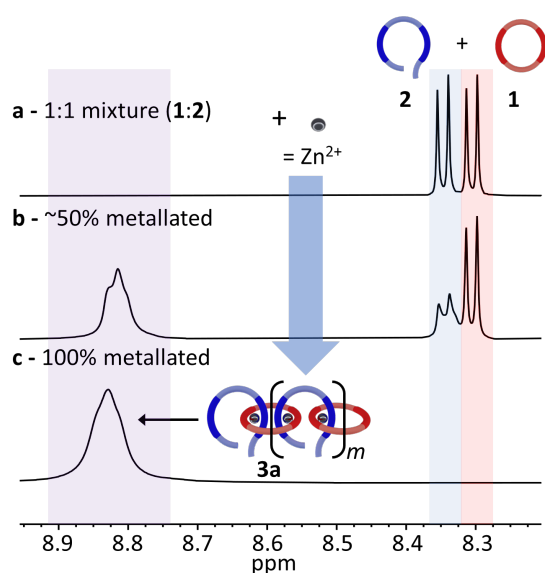


Fig. 4 The region of the ¹H NMR (500 MHz, 298 K) corresponding to the H_{mpy} protons peaks of (a) a 1:1 mixture of macrocycle **1** and thread **2** (in CDCl₃), (b) partial metalation of the mixture by titration of Zn(NTf₂)₂ (in CD₃CN) and (c) the MSP **3a** (in 1:5 CD₃CN:CDCl₃, 20 mM w.r.t. **2**).

Results and Discussion

Analysis of MSP

As the nature of the assembled MSP template is critical to the final product distribution, initial studies focused on obtaining a better understanding of the MSP assembly. A 1:1 mixture of macrocycle **1** and thread **2** in CDCl₃ was prepared and titrated with zinc di[bis(trifluoromethylsulfonyl)imide] (Zn(Tf₂N)₂). 2D NMR studies^{35,36} have shown that the most downfield shifted proton corresponds to the meta-proton of the pyridine moiety of the Bip ligands (H_{mpy}, Figure 2b), which appear at 8.30 ppm and 8.35 ppm for **1** and **2**, respectively (Figure 4a). Coordination of the Zn²⁺ ions with the Bip ligand can be followed by ¹H NMR as the peaks corresponding to H_{mpy} shift to ca. 8.82 ppm (Figure 4b). It is worthwhile noting that the metal-ligand complex and the uncomplexed ligand are in slow exchange on the NMR timescale, allowing for the amount of free species present to be monitored during the titration. The Zn²⁺ ions are added into

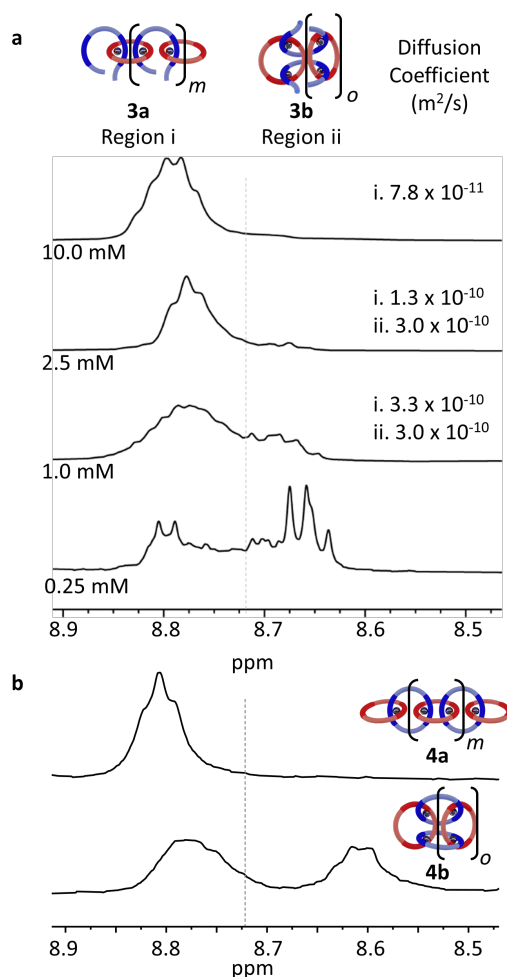


Fig. 5 Region of the ¹H NMR spectra (500 MHz, 1:5 CD₃CN:CDCl₃, 298 K) corresponding to the H_{mpy} protons for (a) the MSP (**3a/3b**) at 0.25 mM, 1.0 mM, 2.5 mM, and 10.0 mM (w.r.t. **2**) along with the diffusion coefficients associated with region i and ii at the different concentrations and (b) for poly[*n*]catenanes **4a** and **4b**.

the reaction mixture until all the H_{mpy} peaks around 8.30–8.35 disappear (Figure 4c). As both Bip moieties in macrocycle **1** cannot bind to the same Zn^{2+} ion,³⁶ the only way for all the Bip ligands to bind a Zn^{2+} ion is the self-assembly of MSP (**3**) that has alternating **1** and **2** units along its backbone.

In order to better understand if/how the MSP changes with concentration, it was dried and then redissolved in a mixture of acetonitrile- d_3 and chloroform- d (1:5) to obtain a series of samples at different concentrations, 0.25 mM, 1.0 mM, 2.5 mM, and 10.0 mM with respect to **2** (Figure 5a, S1). The solutions were then characterized using a combination of ^1H NMR and diffusion ordered spectroscopy (DOSY). At the highest concentration (10.0 mM), the H_{mpy} appears almost entirely as a one broad peak at around 8.8 ppm (Figure 5a, Region i) which was assigned to the formation of MSP **3a** (and/or very large cyclic **3b**). This peak appears similar to what is seen at 20 mM (Figure 4c) during sample preparation. There is a slight shift upfield of this peak at this lower concentration, but no free ligand is observed (Figure 5a). As the concentration decreases, a second set of peaks appear upfield (around 8.67, Region ii in Figure 5a) which grow in intensity at lower concentrations. The dynamic nature of the Zn^{2+} /Bip complex results in a ring-chain equilibria existing in these MSPs and, as rings are more likely to be formed at lower concentrations,³⁷ this suggests that the more upfield shifted Region ii peaks correspond to the cyclic MSP **3b**.

DOSY NMR of the MSP at the different concentrations provided information on the size of the compounds that correspond to the two regions in the NMR. Note: the 0.25 mM sample was too dilute to obtain reliable DOSY data. The diffusion coefficients (Figure S2–4) for Region i decrease from $3.3 \times 10^{-10} \text{ m}^2/\text{s}$ to $7.8 \times 10^{-11} \text{ m}^2/\text{s}$ as the concentration increases from 1 to 10 mM, consistent with an increase in assembly size/MSP molecular weight with concentration, as would be expected for the linear MSP **3a**. Region ii, on the other hand, exhibits similar diffusion coefficients for the concentrations tested. In addition, the diffusion coefficient of the Region ii protons ($3.0 \times 10^{-10} \text{ m}^2/\text{s}$) is similar to the diffusion coefficient of the individual thread (3.0×10^{-10}) or macrocycle (3.8×10^{-10}), suggesting that the MSP in this region is a more compact structure. Taken together, this data is consistent with Region ii corresponding to smaller cyclic MSP assemblies (**3b**).

If these two regions in the NMR are representative of cyclic and linear MSPs, then it could be expected that a similar difference in the NMR would be observed in the metallated catenanes. Thus, using literature procedures³⁵ samples that primarily consist of cyclic polycatenane (**5b**) (via Fe^{2+} templated synthesis³⁵) or linear polycatenane (**5a**) (obtained by SEC purification of the polycatenane synthesis³⁵) were re-metallated with $\text{Zn}(\text{Tf}_2\text{N})_2$ to yield **4a** and **4b**. As can be seen in Figure 5b, the ^1H NMR of cyclic **4b** resembles that of the 0.25 mM MSP, with two broad peaks between 8.60–8.90 ppm. This provides further support to the upfield shifted peaks observed in the more dilute MSPs corresponding to the cyclic assemblies. Likewise, the ^1H NMR of **4a** only shows a broad peak in Region i (around 8.8 ppm) consistent with the MSP at 10.0 mM (Figure 5a, top) being predominantly linear **3a**.

NMR Analysis of Poly[*n*]catenane

To carry out the olefin metathesis ring closing reaction, the MSPs were dried and dissolved in dry dichloromethane to yield a series of samples at 0.25, 0.5, 1.0, 2.5, 5.0, and 10.0 mM, with respect to **2**. It is worthy of note that MSP in dichloromethane- d (Figure S5) shows a similar ^1H NMR Region i and Region ii distribution to that in figure 5a. The Hoveyda Grubbs catalyst (0.32 mM) was added to each reaction before it was heated to reflux for 48 hrs, with a second addition of the same amount of catalyst after the first 24 hours elapsed. After deactivation of the catalyst, the crude material is demetallated using diethylenetriamine.

Figure 6a shows the *m*-pyridyl proton (H_{mpy}) region of the ^1H NMR spectra for each of the demetallated crude reaction mixtures (the full NMR can be found in Figure S6). The non-

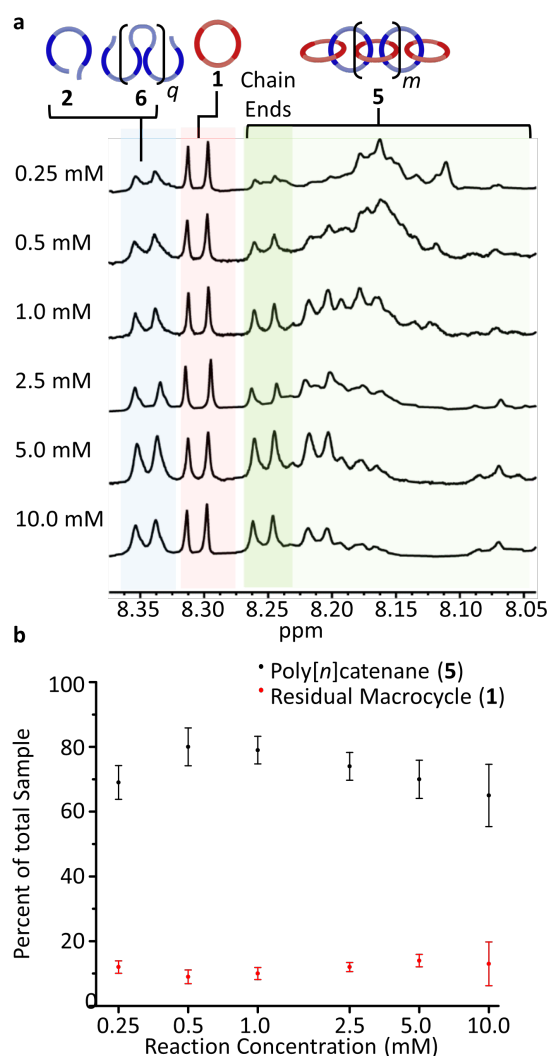


Fig. 6 (a) Region of the ^1H NMR spectra (500 MHz, CDCl_3 , 298 K) corresponding to the H_{mpy} protons for the demetallated crude reaction mixtures at different concentrations. (b) Average poly[*n*]catenane (**5**) (black) yields and amount of residual macrocycle (**1**) at reaction Error bars for data sets taken at 95% confidence interval ($n=5$).

interlocked byproducts are easily identifiable in the NMR, with the macrocycle **1** at 8.31 ppm and the thread **2** and thread-based byproduct **6** around 8.35 ppm. For the interlocked compounds, the H_{mpy} 's shift upfield to between 8.05–8.27 ppm.³⁵ The integration of these peaks allows determination of the average interlocked yield of each reaction (Figure 6b and Table S1). Within this region, a triplet from the **2/6** byproducts appears centered at 8.07 ppm which is excluded from the integration to more accurately calculate the yield of interlocked products (Figure S7). These integrations also allow for a determination of the residual macrocycle (**1**) (Figure 6b) and residual thread (**2**)/ADMET (**6**) yields (Table S1). The crude NMRs can also provide preliminary data on the yield of cyclic catenane (**5b**) via the previously reported³⁵ calculation method (Eq. S2, Figure S7). This cyclic yield (Figure S8) was found to follow a similar trend to the amount of cyclic MSP (**3b**) given for each concentration (Figure S9). The 2.5 mM reaction has an average interlocked yield of ca. $73 \pm 5\%$ ($n = 5$), consistent with the previously reported value.³⁵ The average interlocked yield remains above 70% for all concentrations except those at the extremes (0.25 mM and 10.0 mM). This is in part a consequence of a lower average alkene conversion (87% for both 0.25 and 10.0 mM, c.f. 0.5–2.5 mM show ca. 95% conversion). Presumably at 0.25 mM, the relatively high dilution leads to a decrease in reaction rate and a slightly lower yield of interlocked materials ($69 \pm 5\%$). It is important to note that, at the higher concentrations (5 and 10 mM), a significant amount of insoluble product is obtained during the reaction. This product was still insoluble after demetallation and was only observed to swell in a range of organic solvents, such as chloroform and tetrahydrofuran. These products are assumed to be interlocked networks and are included in the overall interlocked yield in Figure 6b. None-the-less, at 10 mM, the interlocked yield was only $65 \pm 10\%$. This lower value may result from partial insolubility of the both the MSP and the partially reacted species at these higher reaction concentrations. Additionally, the higher concentration will likely promote inter-MSP reactions, resulting in an increased formation of ADMET polymer **6**. Preliminary data from DOSY NMR analysis demonstrated a consistent decrease in diffusion coefficient as the reaction concentration increased (Figure S10, Table S1), suggesting that the higher reaction concentrations yielded larger products.

GPC Analysis of Poly[*n*]catenane Architecture

To fully determine the extent of the size variations between reaction concentrations, the crude products were then analyzed via GPC-MALS. While initial studies of the poly[*n*]catenanes via GPC studies were conducted in THF,³⁵ it was found that a 1:3 mixture of DMF:THF was a better mobile phase for these polymers. In addition, a GPC column with better low molecular weight resolution (relative to the prior studies)³⁵ was employed to allow better resolution of such species. While the resulting GPC traces for the poly[*n*]catenane samples (Figure 7a, Figure S11–16) clearly show that a complicated range of products are formed during these reactions, it is possible to

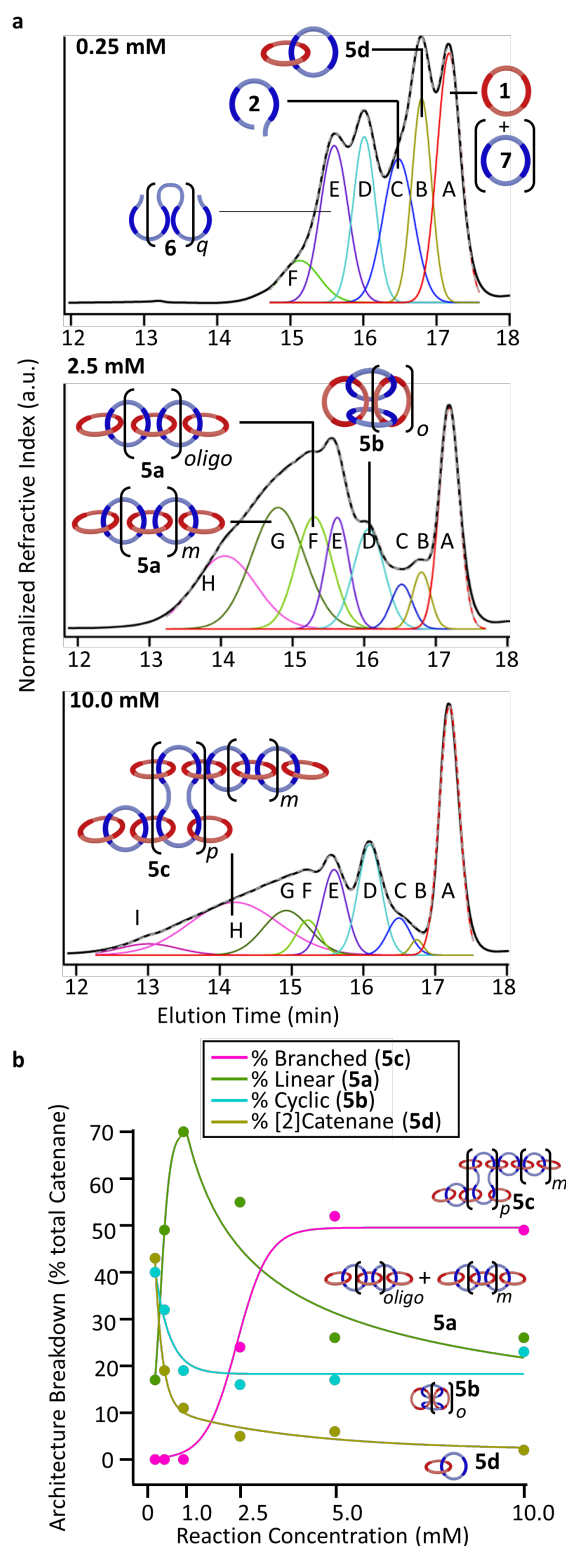


Fig. 7 (a) GPC refractive index traces for 0.25, 2.5, and 10.0 mM (mobile phase ~ 25% DMF in THF). Each trace shows deconvoluted peaks using a Gaussian Fit with each peak showing its (tentative) assignment. (b) Poly/oligo[*n*]catenane (**5a**, **5b**, **5c** (+ insoluble fraction), and **5d**) distribution versus reaction concentration (byproducts are excluded).

draw some conclusions from this data. Perhaps the most obvious data trend is a move to faster elution times with the reactions carried out at the higher concentrations, confirming the formation of higher molecular weight species in these more concentrated reactions. It is also possible to clearly see the presence of the residual macrocycle **1** in all the GPC spectra, which is consistent with what is observed in the NMR. In an attempt to obtain more information on the reaction products, deconvolution of the GPC traces was explored using a gaussian algorithm^{38–40} to fit the data to the minimum number of peaks (see SI for more details). As can be seen in Figure 7 (and Figures S12, 13, 15) excellent fits to the experimental GPC trace can be obtained using 6–9 gaussian peaks (depending on the concentration of the reaction). Pure samples of macrocycle **1** and thread **2** were run using the same conditions and eluted at 17.2 minutes and 16.5 minutes, respectively (Figure S17), allowing those deconvoluted peaks (macrocycle (A, red) and thread (C, blue)) to be assigned to these starting materials. In addition, macrocycle **7**, which can be formed by ring closing of thread **2**, elutes ca. 17.3 minutes and as such, if present, would also be present as part of deconvoluted peak A (red).

Between the macrocycle peak (A, red) and the linear thread peak (C, blue) there is a peak that elutes at approximately 16.8 minutes (B, gold in Figure 7). Based on the elution time of this peak, this compound is more compact than the thread (**2**) but bigger than macrocycles **1** and **7**. MALS data corresponding to this peak (Figures S11–16) shows that the molecular weight of this compound is approximately double that of macrocycle peak A. This suggests that peak B either corresponds to a [2]catenane

(**5d**) and/or possibly the non-interlocked cyclic dimer of thread **2**. The fact that this peak is more prominent at the lowest concentration (0.25 mM, Figure 5 top), is consistent with either of these assignments.

Peak D (cyan in Figure 7a) elutes at 16.0 minutes and is assigned as the cyclic catenane **5b**, as it corresponds to the elution time of a purified cyclic sample, with an average of 5 rings, based on MALS data (Figure S17).³⁵ The next identified peak elutes at approximately 15.6 minutes (Peak E, purple, Figure 7a). While this peak does not correspond to any isolated samples, it is tentatively assigned to the ADMET (**6**) product in each of the samples.

Based on the previous poly[*n*]catenane characterization,³⁵ it is proposed that Peaks F, G, H, and I correspond to different populations of linear (**5a**) and branched (**5c**) poly[*n*]catenanes. There are a number of different routes that linear poly/oligo[*n*]catenanes can be accessed during the synthesis. Figure 8 highlights two possible routes to these structures, namely incomplete ring closing of the linear (**3a**) and cyclic (**3b**) MSPs. It can be expected that at low concentrations (when most of the MSP is the cyclic **3b**, see above) the majority of the linear catenane will be formed via **3b** while at higher concentrations the linear catenane will be accessed predominantly via **3a**. If both of these routes occur simultaneously, it can then be expected that there will be two molecular weight populations of linear **5a**. These two populations are tentatively assigned to Peaks F and G (light and dark green) based on the GPC elution time of a sample of purified primarily linear (**5a**) poly[*n*]catenane (Figure S17) that spans both peaks.

For the 0.25 mM sample, where the MSP is almost exclusively cyclic **3b**, only Peak F is present (15.2 minutes, light green). Based on MALS analysis of this peak, it corresponds to relatively low molecular weight oligomers/catenanes (average molecular weight M_n ca. 8 kg/mol). For this reaction, the ¹H NMR of the sample shows evidence of catenane chain ends (Figure 6a), indicating a mixture of linear **5a** and cyclic **5b** poly[*n*]catenanes. As such, it is proposed that Peak F corresponds to the linear oligo[*n*]catenanes **5a** formed from via the cyclic MSP (Figure 8). This hypothesis is supported by the fact that peak F corresponds to a smaller percentage of the overall product distribution at higher concentrations (Table S2). NMR of the MSP shows that, as the reaction concentration increases, the MSP shifts from being predominantly cyclic (**3b**) to being predominately linear (**3a**), resulting in a decrease in the yield of this oligomeric linear catenane (**5a**) at higher concentrations. As the relative size of peak F decreases with reaction concentration there is a concomitant appearance and increase in the size of Peak G. It is proposed that Peak G corresponds to the higher molecular weight linear catenanes that result from the successful ring-closing of the linear MSP **3a** (Figure 8).

Peaks H and I correspond to the largest molecular weights observed in the catenanes. Based on chain end analysis of fractionated samples in prior work and comparison to an isolated branched poly[*n*]catenane sample (Figure S17), these peaks are tentatively assigned to branched **5c** poly[*n*]catenanes. Peak H (light pink) at 14.1, begins to appear at 2.5 mM (Figure 7a middle), where the presence of branched catenanes has

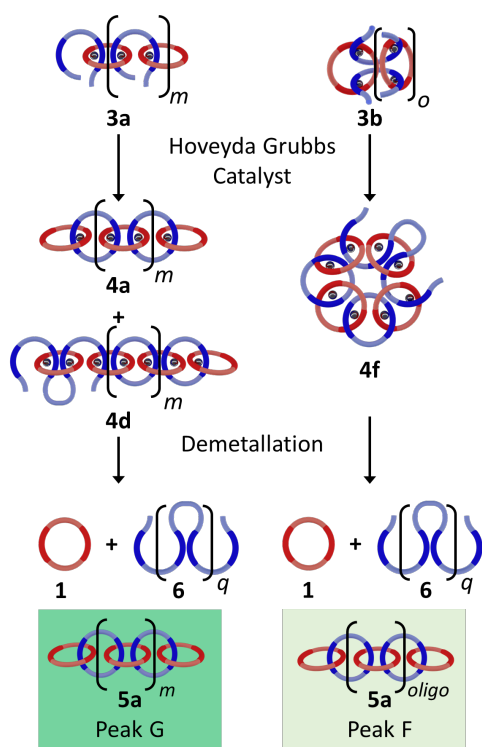


Fig. 8 Proposed routes to linear poly/oligo[*n*]catenanes (**5a**) with different molecular weight populations (byproducts are excluded).

already been reported.³⁵ As the concentration increases further however, a second peak (Peak I, dark pink) at 13.0 minutes is required for the Gaussian fit (Figure 7a bottom, Table S2), suggesting the formation of a new population of highly branched polymers (MALS, $M_n = 60$ kg/mol, $\overline{DP} = 39$ (Eq. S1)). Based on these peak assignments, some general trends can be elucidated (Figure 7b Table S2) regarding the impact of reaction concentration on product distribution. As may be expected, the [2]catenane (**5d**) (and/or cyclic dimer of **2**) and the cyclic (**5b**) catenanes are the dominant products at the lowest concentration (0.25 mM). As the reaction concentration increases, the yields of **5d/2** and **5b** drop and eventually plateau for concentrations between 2.5 - 10 mM.⁴¹

The linear (**5a**) catenanes (polymer + oligomer) show a significant increase in yield from 0.25 mM to 1.0 mM (Figure 7b, green) and become the dominant product (70% **5a** at 1.0 mM). However, the linear **5a** formed at 1.0 mM appears to be primarily oligomeric in nature (peak F), presumably a consequence of being formed predominantly from the cyclic MSP precursor (**3b**). While increasing the reaction concentration to 2.5 mM results in a slight drop in the overall yield of linear **5a** (Figure 8), the resulting **5a** now is predominately the higher molecular **5a** fraction (Peak G). As a result, carrying out this reaction at 2.5 mM optimizes both the yield and molecular weight of the linear **5a** products. Between 2.5-5.0 mM the overall amount of linear polycatenane decreases as branched poly[*n*]catenanes **5c** (Figure 7a, pink) start to be formed. It is worthwhile also noting that at the higher concentrations, the larger molecular weight fraction (Figure 7a, Peak G) of linear polycatenane **5a** becomes the dominant linear species. However, the yield of the branched polycatenanes (**5c** plus networks as these numbers also include insoluble polymers) quickly dominates the reaction products, becoming the major poly[*n*]catenane formed above 5.0 mM (52% **5c**) and 10.0 mM (48% **5c**).

Chain End Analysis via GPC/NMR Techniques

One way to further elucidate the trends in architecture (and to back up the assignment of the deconvoluted peaks in the GPC) is to determine the number of average numbers of chain ends (N_c) in each sample. For these samples, cyclic poly[*n*]catenanes have no chain ends ($N_c = 0$), linear poly[*n*]catenanes have $N_c = 2$ and branched poly[*n*]catenanes have $N_c \geq 3$, therefore determination of the average number of chain-ends in the sample can give an idea of the architecture distribution. Using a qualitative assessment of the ¹H NMR data in Figure 6a, the chain end region from 8.24-8.27 reflects the observed GPC trends: products formed at low reaction concentrations show diminutive peaks in this region, reflecting fewer chain ends and the primarily cyclic nature of the materials. However, at the higher reaction concentrations the products show increased prevalence of these chain end peaks consistent with the transition into linear and highly branched materials.

To quantify this analysis, a new set of poly[*n*]catenanes were synthesized and were partially purified using literature procedures before analysis.³⁵ This purification was performed in

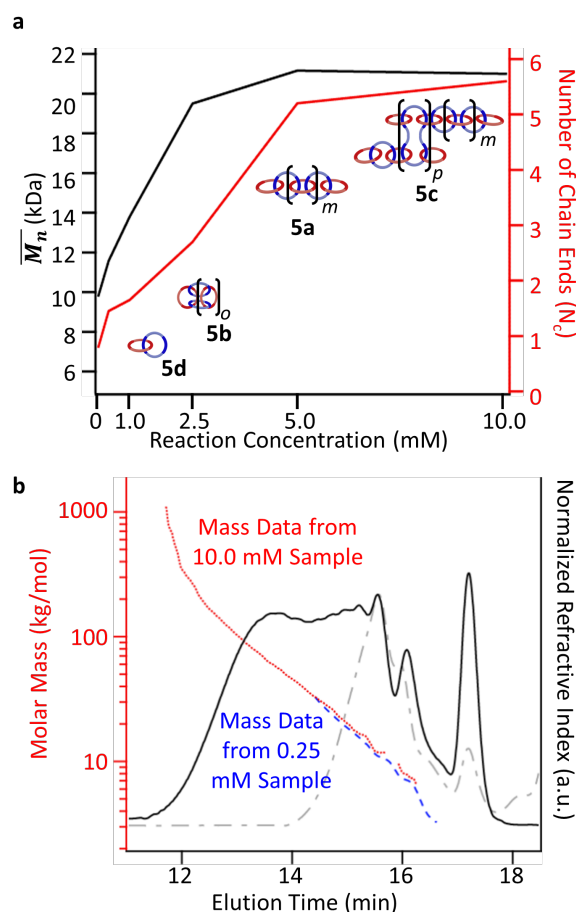


Fig.

9 (a) Number average molar mass (M_n) determined by GPC-MALS plotted for the reaction concentrations to observe the trends. Number of chain ends (N_c) determined by a combination of GPC-MALS and NMR analysis.²⁹ (b) GPC RI trace from the 10.0 mM (black) and 0.25 mM (grey, dash) purified sample. Absolute molecular weight (determined by MALS) for the 10.0 mM purified sample (red, dots) and the 0.25 mM purified sample (blue, dashes).

an attempt to remove as much of the byproducts as possible, particularly ADMET **6**, to minimize the influence of these byproducts on the reported poly[*n*]catenane molecular weight and calculated N_c .

For this purification, the poly[*n*]catenanes were partially remetalated with Zn^{2+} ions and the mixture was dried and washed with 2:1 chloroform:hexanes to remove the soluble unmetallated (by)products (see SI and previous work³⁵ for more details on the purification procedure). These samples were then demetalated and analyzed by GPC MALS (using 25 vol% DMF in THF as the mobile phase) and ¹H NMR. Figure 9a shows the M_n and calculated average number of chain ends (N_c), determined by a combination of the NMR and the GPC-MALS data using previously published procedures (Eq. S3).³⁵ For example, based on this combination of NMR and GPC-MALS data, the poly[*n*]catenanes prepared at 2.5 mM have an average number of chain-ends of ca. 2.7, consistent with the product architecture being predominantly linear (**5a**) with some branched. In fact, deconvolution of the GPC trace (Figure S18) shows the dominance of the linear poly[*n*]catenane assigned peak G (50 % of the total catenated material) in this sample.

The data obtained from the partially purified samples also allows for a more complete analysis of the molecular weight trends throughout the various concentrations with the reduced presence of ADMET **6** (Figure S19). Consistent with the prior data, lower molecular weights result from the samples where the primary starting material was the cyclic MSP **3b**. For these, at 0.25 mM and 0.5 mM, the average molecular weight appeared as 9.8 and 11.6 kg/mol respectively. These would correspond to catenanes with approximately 6 and 8 interlocked macrocycles. For both of these samples, chain end analysis³⁵ revealed that the average poly[*n*]catenane contained fewer than 2 chain ends (0.8, 1.5, Figure 9a) demonstrating that the material was likely a combination of the [2]catenane (**5d**), oligomeric **5a**, and cyclic **5b** poly[*n*]catenanes.

At higher concentrations the MSP precursor shifts to a higher percentage of the linear (**3a**) and as such the resulting products now consist of more linear (**5a**) and branched (**5c**) poly[*n*]catenanes ($N_c > 2$). This is concomitant with an increase of the $\overline{M}_n$ for the samples: at 2.5 mM the $\overline{M}_n$ is 19.5 kg/mol, ($\overline{DP}$ ca. 13) and N_c is 2.7. At this reaction concentration, the GPC MALS trace also shows evidence of larger catenanes, with molecular weights up to 100 kg/mol.

The highest reaction concentration studied (10.0 mM) produces the highest molecular weight species, $\overline{M}_n$ of 21 kg/mol ($\overline{DP}$ ca. 14). The poly[*n*]catenanes synthesized here exhibit the largest N_c (5.6), indicative of the presence of a significant amount of highly branched poly[*n*]catenanes. It is important to note that this molecular weight analysis includes the lower molecular weight products (ADMET (**6**), cyclic (**5b**), and [2]catenane (**5d**)) that were not completely removed during the partial purification step, suggesting that the average size of the linear **5a** and branched **5c** materials is larger than this value.

For comparison Figure 9b shows the GPC-MALS data for these partially purified reactions mixtures that were obtained at 0.25 and 10 mM. The highest molecular weight products obtained at 0.25 mM are ca. 33 kg/mol. However, the MALS data of products obtained from the 10mM show evidence of soluble (branched) catenanes up to 1000 kg/mol ($DP > 640$), which are the largest reported poly[*n*]catenane compounds to date.

Conclusions

This study has been able to clarify several aspects of synthesis of poly[*n*]catenanes from an MSP template. The combination of carrying out the reaction at different concentrations along with analysis of the crude reaction mixture has shown how the architecture of the resulting poly[*n*]catenane can be altered. At low concentrations, cyclic and oligomeric linear poly[*n*]catenanes will predominate, while at the highest reaction concentrations, high molecular weight branched poly[*n*]catenanes are the major product, with poly[*n*]catenanes of up to 1000 kg/mol being observed. The formation of insoluble but swellable materials at these higher reaction concentrations may suggest the formation of interlocked networks and current research is underway to better characterize and understand these materials.

Author Contributions

SJR and QW proposed the study. QW conducted preliminary studies and provided a set of comparative poly[*n*]catenanes. All further synthesis and analysis were conducted by MMT. SJR supervised the work. MMT and SJR wrote the manuscript. All authors discussed and commented on the manuscript.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work was funded by National Science Foundation (NSF) grant number CHE-1903603. Parts of this work were carried out at the Soft Matter Characterization Facility of the University of Chicago. We would like to thank the director of this facility, Dr. Phillip Griffin, for assistance with GPC characterization. We would like to thank the University of Chicago Chemistry NMR Facility and the facility managers past and present, Dr. Antoni Jurkiewicz and Dr. Josh Kurutz. Finally, we would like to acknowledge Dr. Benjamin Rawe for his intellectual contributions to this work.

References

- 1 H. L. Frisch and E. Wasserman, *J. Am. Chem. Soc.*, 1961, **83**, 3789–3795.
- 2 E. Wasserman, *J. Am. Chem. Soc.*, 1960, **82**, 4433–4434.
- 3 J.-P. Sauvage, *Angew. Chemie - Int. Ed.*, 2017, **56**, 11080–11093.
- 4 B. L. Feringa, *Angew. Chemie Int. Ed.*, 2017, **56**, 11060–11078.
- 5 J. F. Stoddart, *Angew. Chemie Int. Ed.*, 2017, **56**, 11094–11125.
- 6 A. Harada, *Nature*, 1992, **356**, 325–327.
- 7 Z. Niu and H. W. Gibson, *Chem. Rev.*, 2009, **109**, 6024–6046.
- 8 L. Fang, M. A. Olson, D. Benitez, E. Tkatchouk, W. A. Goddard III and J. F. Stoddart, *Chem. Soc. Rev.*, 2010, **39**, 17–29.
- 9 M. Arunachalam and H. W. Gibson, *Prog. Polym. Sci.*, 2014, **39**, 1043–1073.
- 10 T. Takata, N. Kihara and Y. Furusho, *Adv. Polym. Sci.*, 2004, **171**, 1–75.
- 11 L. F. Hart, J. E. Hertzog, P. M. Rauscher, B. W. Rawe, M. M. Tranquilli and S. J. Rowan, *Nat. Rev. Mater.*, DOI:10.1038/s41578-021-00278-z.
- 12 T. Takata, *Polym. J.*, 2006, **38**, 1–20.
- 13 H. Xing, Z. Li, Z. L. Wu and F. Huang, *Macromol. Rapid Commun.*, 2018, **39**, 1700361.
- 14 W. Wang and H. Xing, *Polym. Chem.*, 2018, **9**, 2087–2091.
- 15 P. M. Rauscher, K. S. Schweizer, S. J. Rowan and J. J. de Pablo, *Macromolecules*, 2020, **53**, 3390–3408.
- 16 P. M. Rauscher, S. J. Rowan and J. J. de Pablo, *ACS Macro Lett.*, 2018, **7**, 938–943.

- 17 P. M. Rauscher, K. S. Schweizer, S. J. Rowan and J. J. de Pablo, *J. Chem. Phys.*, 2020, **152**, 214901.
- 18 H. C. Renger and D. R. Wolstenholme, *J. Cell Biol.*, 1972, **54**, 346–364.
- 19 G. Riou and E. Delain, *Proc. Natl. Acad. Sci.*, 1969, **62**, 210–217.
- 20 P. Borst and J. H. J. Hoeijmakers, *Plasmid*, 1979, **2**, 20–40.
- 21 D. B. Amabilino, P. R. Ashton, A. S. Reder, N. Spencer and J. F. Stoddart, *Angew. Chemie Int. Ed. English*, 1994, **33**, 1286–1290.
- 22 C. H. Lu, X. J. Qi, A. Cecconello, S. S. Jester, M. Famulok and I. Willner, *Angew. Chemie - Int. Ed.*, 2014, **53**, 7499–7503.
- 23 H. Iwamoto, S. Tafuku, Y. Sato, W. Takizawa, W. Katagiri, E. Tayama, E. Hasegawa, Y. Fukazawa and T. Haino, *Chem. Commun.*, 2016, **52**, 319–322.
- 24 N. Watanabe, Y. Ikari, N. Kihara and T. Takata, *Macromolecules*, 2004, **37**, 6663–6666.
- 25 J. A. Berrocal, L. M. Pitet, M. M. L. Nieuwenhuizen, L. Mandolini, E. W. Meijer and S. Di Stefano, *Macromolecules*, 2015, **48**, 1358–1363.
- 26 K. Endo, T. Shiroy, N. Murata, G. Kojima and T. Yamanaka, *Macromolecules*, 2004, **37**, 3143–3150.
- 27 K. Endo and T. Yamanaka, *Macromolecules*, 2006, **39**, 4038–4043.
- 28 H. Xing, Z. Li, W. Wang, P. Liu, J. Liu, Y. Song, Z. L. Wu, W. Zhang and F. Huang, *CCS Chem.*, 2019, **1**, 513–523.
- 29 B. Nisar Ahamed, R. Duchêne, K. Robeyns and C.-A. Fustin, *Chem. Commun.*, 2016, **52**, 2149–2152.
- 30 N. H. Evans and P. D. Beer, *Chem. Soc. Rev.*, 2014, **43**, 4658–4683.
- 31 J. E. Beves, B. A. Blight, C. J. Campbell, D. A. Leigh and R. T. McBurney, *Angew. Chemie - Int. Ed.*, 2011, **50**, 9260–9327.
- 32 M. Denis and S. M. Goldup, *Nat. Rev. Chem.*, , DOI:10.1038/s41570-017-0061.
- 33 J. P. Sauvage and J. Weiss, *J. Am. Chem. Soc.*, 1985, **107**, 6108–6110.
- 34 F. Diederich, P. J. Stang and R. R. Tykwinski, Eds., *Modern Supramolecular Chemistry*, Wiley, 2008.
- 35 Q. Wu, P. M. Rauscher, X. Lang, R. J. Wojtecki, J. J. de Pablo, M. J. A. Hore and S. J. Rowan, *Science (80-)*, 2017, **358**, 1434–1439.
- 36 R. J. Wojtecki, Q. Wu, J. C. Johnson, D. G. Ray, L. S. T. J. Korley and S. J. Rowan, *Chem. Sci.*, 2013, **4**, 4440–4448.
- 37 J. D. Fox and S. J. Rowan, *Macromolecules*, 2009, **42**, 6823–6835.
- 38 S. A. Mirmohammadi, M. Imani, H. Uyama, M. Atai, M. B. Teimouri and N. Bahri-Lale, *Polym. Int.*, 2014, **63**, 479–485.
- 39 N. Cozza, W. Bonani, A. Motta and C. Migliaresi, *Int. J. Biol. Macromol.*, 2016, **87**, 504–513.
- 40 Y. Zheng, Y. Huang and B. C. Benicewicz, *Macromol. Rapid Commun.*, 2017, **38**, 1700300.
- 41 J. A. Semlyen, in *Mechanisms of Polyreactions-Polymer Characterization*, Springer Berlin Heidelberg, Berlin, Heidelberg, pp. 41–75.