ARTICLE

Received 00th January 20xx, Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

Paired Electrolysis of 5-(Hydroxymethyl)furfural in Flow Cells with High-Performance Oxide-Derived Silver Cathode

Hengzhou Liu, a Ting-Han Lee, a Yifu Chen, Eric W. Cochran, a Wenzhen Lia

Electrocatalytic upgrading of biomass-derived feedstocks driven by renewable electricity offers a greener way to reduce the global carbon footprint associated with the production of value-added chemicals. In this respect, a key strategy is the electrocatalytic hydrogenation (ECH) reaction, which is typically paired with the anodic oxygen evolution reaction (OER) with sluggish kinetics, producing O_2 with little value. Here we prepared an oxide-derived Ag (OD-Ag) electrode with high activity and up to 98.2% selectivity for the ECH of 5-(hydroxymethyl)furfural (HMF) to 2,5-bis(hydroxymethyl)furan (BHMF), and such efficient conversion was achieved in a three-electrode flow cell. The excellent BHMF selectivity was maintained over a broad potential range with long-term operational stability. We then considered the oxidation of HMF to 2,5-furandicarboxylic acid (FDCA) and hydrogen (to water) as more efficient and productive alternatives to the OER. In HMF-to-BHMF paired with 2,2,6,6-tetramethylpiperidine 1-oxyl (TEMPO)-mediated HMF-to-FDCA conversion, a markedly reduced cell voltage from ~7.5 V to ~2.0 V was observed by transferring the electrolysis from the H-type cell to the flow cell, corresponding to more than four-fold increase in energy efficiency in operation at 10 mA. A combined faradaic efficiency of 163% was obtained to BHMF and FDCA. Alternatively, the anodic hydrogen oxidation reaction on platinum further reduced the cell voltage to only ~0.85 V at 10 mA. These paired processes show the potential for integration of renewable electricity and carbon for green and economically feasible distributed chemical manufacturing.

Introduction

Electrocatalytic conversions of biomass-derived feedstocks, particularly driven by renewable electricity sources from wind and sunlight, have attracted enormous attention. Replacing fossil-based processes with renewable energy reduces the emission of greenhouse gases and helps mitigate their adverse impact on the environment. The driving force of electrochemical reactions is the electrode potential instead of thermal energy, with "clean" electrons as the reducing and oxidizing agents rather than toxic reductants and oxidants. However, in many circumstances, the complementary reaction at the counter electrode has sluggish kinetics and yields low-value products. For instance, the anodic four-electron oxygen evolution reaction (OER) is unfavorable both thermodynamically and kinetically, and produces O_2 with little value. Indeed, it was found that the anodic OER consumes $\sim 90\%$ of the full cell voltage and energy consumption in CO_2 electro-reduction processes.

Pairing two desirable electrochemical half-reactions in one reactor can achieve the co-generation of valuable chemicals and fuels at both cathode and anode, which is regarded as a promising approach to increase energy efficiency and economic feasibility.⁵

E-mail: wzli@iastate.edu, ecochran@iastate.edu

H.L. and T. L. contributed equally to this work.

Ideally, a 200% theoretical faradaic efficiency (FE) to desired products can be obtained, doubling the conventional cells with only one desirable half-reaction. Moreover, pairing one electrochemical half-reaction more favorable than OER at the anode or hydrogen evolution reaction (HER) at the cathode can significantly lower the cell voltage, and hence, the overall energy consumption, as suggested by the recent techno-economic study. 6 Some examples of paired electrolysis have been demonstrated, such as CO₂ reduction coupled with organic oxidations4, 7-11 or oxidative treatment of nitrogenous wastes, 12 and co-electrolysis of two organics. 13-16 To date, reports of paired electrolysis have mainly been proof-ofconcept studies conducted in H-type reactors in order to evaluate electrolysis performances; 13, 17 however, the high energy cost and operational inefficiencies associated with the H-cells are critical barriers to further development of the economically feasible scaleup design of such processes. 18 In this regard, continuous operation in a flow reactor can greatly reduce the ohmic loss, thus improving the energy efficiency. In addition, the enhanced mass transport would be desirable for scale-up studies for economically-feasible electrosynthesis.

5-(hydroxymethyl)furfural (HMF) has been listed as one of the "top 10" biobased chemicals by the U.S. Department of Energy as a platform for value-added products. ^{19, 20} Its hydrogenation product 2,5-bis(hydroxymethyl)furan (BHMF) is an essential precursor for the production of polyesters and resins. ²¹ Its oxidation product 2,5-furandicarboxylic acid (FDCA) is a feedstock to produce renewable polymers such as polyethylene 2,5-furandicarboxylate (PEF) as a promising alternative to polyethylene terephthalate (PET). ²² Electrochemical conversions of HMF have been studied in recent years, such as its electrocatalytic hydrogenation (ECH) to BHMF on

^a Department of Chemical and Biological Engineering, Iowa State University, 618 Bissell Road, Ames, IA 50011, USA.

[†]Electronic Supplementary Information (ESI) available: [details of any supplementary information available should be included here]. See DOI: 10.1039/x0xx00000x

Ag-based catalysts , ^{17, 23} and electrocatalytic oxidation (ECO) to FDCA via a redox mediator²⁴ or on Ni- and Co-based catalysts in alkaline electrolytes. ²⁵⁻²⁸ Our previously reported Ag/C catalyst with nanosized Ag showed higher activity than Ag foil, but the carbon support was found to interfere with the HMF reduction pathway, leading to the generation of undesirable dimer product [5,5′-bis(hydroxymethyl)hydrofuroin, BHH] at higher overpotentials. ^{17, 23} Moreover, co-electrolysis by pairing ECH and ECO of HMF in one cell has rarely been reported, especially in flow electrolyzers with optimized cell voltage.

Herein, we demonstrated the significant enhancement in ECH activity for the HMF-to-BHMF reaction on an oxide-derived silver (OD-Ag) electrode compared to Ag foil, alongside 90+% BHMF selectivity in a wide potential range. The excellent performance on OD-Ag is due to its wave-like surface morphology, which provides more active sites and lowers the energy barriers for hydrogen and HMF adsorption. HMF conversion and BHMF selectivity were further improved in a three-electrode flow cell for long-term operations as compared with the H-type cell. Coupling the ECH (HMF-to-BHMF) reaction on OD-Ag with the ECO (HMF-to-FDCA) reaction mediated by (2,2,6,6-tetramethylpiperidin-1-yl)oxyl (TEMPO), a significantly reduced cell voltage from ~7.5 V in the H-type cell to ~2.0 V in the flow cell was achieved, corresponding to more than four-fold increase in energy efficiency at 10 mA. The total FE to BHMF and FDCA of up to 163% was obtained for the co-electrolysis of HMF. The same ECH reaction was also coupled with hydrogen oxidation reaction (HOR) on Pt/C, resulting in a cell voltage of only ~0.85 V at 10 mA. Our paired electrolytic system will facilitate further advancements in coupled processes for efficient and sustainable utilization of bio-derived molecules to produce value-added chemicals with lower energy inputs.

Results and Discussion

Synthesis and characterization of OD-Ag electrocatalyst

OD-Ag was prepared by treating Ag foil with high-frequency (500 Hz) square-wave voltammetry (SWV) followed by constant-potential electrolysis at -1.3 V_{Ag/AgCl} (V_{Ag/AgCl}: V vs. Ag/AgCl, hereinafter). The color of Ag foil periodically changes between white and black during the SWV operation, and a yellow surface was finally obtained after the constant-potential electrolysis (Fig. S1a). These black and yellow layers were AgO_x and OD-Ag, respectively, confirmed by the cyclic voltammogram (CV) under the same alkaline system and the Pourbaix diagram of silver (Fig. S1b-c).²⁹ XRD patterns (Fig. 1a) confirmed the mono-constituent Ag⁰ in OD-Ag. XPS (Fig. 1b) exhibited the same binding energies of Ag $3d_{3/2}$ (374.1 eV) and $3d_{5/2}$ (368.0 eV) for OD-Ag and Ag foil. SEM imaging (Fig. 1c) shows that OD-Ag has a rough surface consisting of around 100-nm particles. AFM analysis (Fig. 1d) revealed that OD-Ag has a periodic wave-like morphology with ± 250 nm of surface depth, in contrast to the smooth surface of Ag foil (Fig. S2). The above characterization results clearly demonstrate the successful preparation of the OD-Ag electrode.

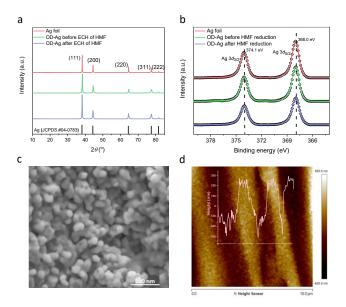


Fig. 1. Physical characterization of OD-Ag electrocatalyst. (a) XRD patterns and (b) XPS Ag 3d spectra of Ag foil, freshly-prepared OD-Ag, and OD-Ag after electrolysis. (c) SEM image of OD-Ag. (d) AFM image of OD-Ag. The inset graph is the height profile of a 6-μm section (the white horizontal line).

ECH of HMF on OD-Ag in H-type cell




Fig. 2. ECH of HMF in the H-type cell. (a) Schematic illustration of the H-type cell for ECH of HMF. (b) Cyclic voltammograms of Ag foil and OD-Ag in 0.5 M borate buffer (pH 9.2) with 20 mM HMF. The geometric area of the electrode was 2 cm² and the scan rate was 20 mV s $^{-1}$. Onset potential was defined as the potential at -1.0 mA cm $^{-2}$ in the negative scan. (c) Product selectivity and conversion of HMF in 0.5 M borate buffer (pH 9.2) with 20 mM HMF on Ag foil (left columns) and OD-Ag (right columns) at different applied potentials for half-hour electrolysis.

It is known that metal electrodes subjected to oxidation-reduction treatment may possess nanostructured surfaces, which could enhance their electrocatalytic performances.^{30, 31} Such enhancement has yet been reported for HMF reduction.

We first performed CV in the electrolyte with 20 mM HMF (Fig. 2a–b). Compared to Ag foil, OD-Ag showed 240 mV of positive shift in onset potential (defined as the potential at -1.0 mA cm $^{-2}$ in the negative scan). The current density on OD-Ag was 2–3 times higher than Ag foil in the measured potential range. Besides, half-hour CA tests showed that OD-Ag delivered not only higher HMF conversion but also higher BHMF selectivity than Ag foil at potentials more negative than -1.25 V_{Ag/AgCl} (Fig. 2c): 90+% of BHMF selectivity was obtained on OD-Ag, in contrast to 67.0–82.9% of selectivity on Ag foil. At -1.25 V_{Ag/AgCl}, the selectivity to dimer product BHH was 10.2% on OD-Ag, much lower than that of 17.3% on Ag foil. In addition, the chemical state of Ag in OD-Ag was unchanged after ECH of HMF (Fig. 1a–b).

Journal Name ARTICLE

Selectivity depicts the distribution of HMF reduction products based on the carbon balance, while FE is defined by the fraction of total charges to produce a certain product. As shown in Fig. 2c and Fig. S4, the selectivity of BHMF increased in line with the increased FE of H₂ (from HER) as the potential became more negative on OD-Ag. Also, the observed FE of H₂ on OD-Ag outperformed that on Ag foil. Such parallel behavior could be attributed to the common reaction intermediate (H_{ads} , generated from $H^+ + e^- \rightarrow H_{ads}$) of ECH and HER; thus, higher coverage of Hads on the electrode surface would increase the BHMF selectivity, and simultaneously sacrifice some charges for H_{ads}-H_{ads} combination to form H₂.³² Apparently, binding of H_{ads} is intrinsically more favorable on the surface of OD-Ag compared to Ag foil. Accordingly, the dimer product BHH becomes less favorable on OD-Ag. As the mechanisms suggested in previous studies, 33, 34 BHH is formed by one adsorbed H coupled with one adsorbed HMF molecule, followed by rapid desorption as free radicals for dimerization before the addition of the second Hads to BHMF. The lower BHH selectivity on OD-Ag could be due to the appropriate binding energy of HMF and its reduction intermediates on the surface for two H_{ads} addition to BHMF instead of one H_{ads} addition to radicals. The above observations essentially stem from the wave-like morphology and higher surface area of OD-Ag, which reduce the energy barriers for the adsorption of both H and HMF.

ECH of HMF on OD-Ag in the three-electrode flow cell

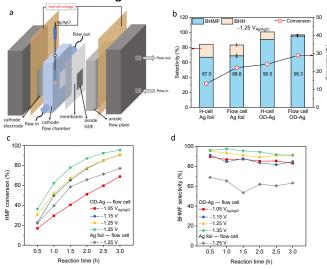


Fig. 3. ECH of HMF in the flow reactor. (a) Schematic illustration of the three-electrode flow cell, where Ag/AgCl was placed in the cathodic spacer to control the applied potential. ECH of HMF was performed on OD-Ag. The anodic reaction was OER. (b) Comparison of product selectivity and HMF conversion on different electrodes and cell configurations at $-1.25~V_{Ag/AgCl}$ for half-hour electrolysis. (c) HMF conversion and (d) BHMF selectivity in three-electrode flow cell on Ag foil and OD-Ag at different potentials for 3-hour electrolysis. The samples were quantified in half-hour intervals. The electrolyte was 0.5 M borate buffer (pH 9.2) with 20 mM HMF. Error bars represent the standard deviation of the mean value from at least three measurements. Detailed experimental setup is shown in Fig. S3.

A three-electrode flow electrolyzer was designed to reduce the limitation of mass transport in the continuous ECH of HMF. As shown in Fig. 3a, the catholyte was fed into a PTFE spacer with the Ag/AgCl reference electrode, and the anolyte was fed via a flow-field plate to a catalyst-supported gas diffusion electrode attached to the anion exchange membrane.

The ECH performances in different cell configurations are compared in Fig. 3b. Both HMF conversion and BHMF selectivity are

higher in the flow cell, following the sequence: OD-Ag in flow cell > OD-Ag in H-type cell >> Ag foil in flow cell > Ag foil in H-type cell. In the flow cell, HMF conversion and BHMF selectivity were also higher on OD-Ag than that on Ag foil (HMF conversion: 28.9% vs. 22.1%; BHMF selectivity: 95.3% vs. 68.8% at $-1.25~V_{Ag/AgCl}$ for half-hour electrolysis), showing the same trend with the measurements in the H-type cell. In addition, with the same electrode of OD-Ag for a half-hour electrolysis, HMF conversion in the flow cell has outperformed the performance in the H-type cell (28.9% vs. 24.0%), benefiting from the enhanced mass transport in the flow reactor.

The superior ECH activity and BHMF selectivity on OD-Ag can be maintained in a broad potential range. As shown in Fig. 3c–d, in 3-hour continuous measurements, the BHMF selectivity maintained 80+% in the potential range of –1.05 to –1.35 V. The high HMF conversion has achieved over 90% at potentials more negative than –1.15 V, which also revealed the superior capability of the flow reactor for continuous ECH of HMF with minimal external mass transport limitations. In addition, the consistent activity obtained on OD-Ag confirmed the high durability and robustness of the system under testing conditions, without significant performance drop issues.

ECH-ECO paired electrolysis in the flow cell

The above experiments were carried out with OER as the anodic reaction, which is known to be thermodynamically and kinetically sluggish. Thermodynamic calculations of the ECH-OER electrolytic system also suggest that the energy consumption is mainly attributed to OER (Eqs. 1–3):

Cathode:

HMF + 2
$$e^-$$
 + 2H₂O → BHMF + 2OH⁻ Δ G° = -23 kJ mol⁻¹ (1)
Anode:

$$2OH^{-} \rightarrow H_{2}O + 0.5O_{2} + 2e^{-} \Delta G^{\circ} = 237.10 \text{ kJ mol}^{-1}$$
 (2)

HMF + H₂O → BHMF + 0.5O₂
$$\Delta G^{\circ}$$
 = 214.10 kJ mol⁻¹ (3)

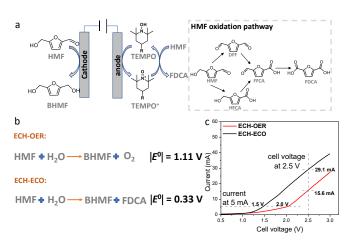


Fig. 4. Comparison of ECH-OER and ECH-ECO paired electrolytic system in the flow reactor. (a) Schematic illustration of ECH-ECO paired electrolytic system, with HMF reduction to BHMF at the OD-Ag cathode and TEMPO-mediated HMF oxidation at the anode. Two possible HMF oxidation pathways^{17, 24} are shown in the dotted box. (b) Calculated thermodynamic cell potentials ($|E^0| = |-\Delta G^*_{cell}/nF|$) of the ECH-OER system and the ECH-ECO system. (c) Linear sweep voltammograms of the ECH-OER and ECH-ECO systems in 0.5 M borate buffer (pH 9.2) with 20 mM HMF. The scan rate was 5 mV s⁻¹.

Alternatively, by replacing anodic OER with the ECO of HMF to a value-added product FDCA (noted as ECH-ECO paired electrolysis),

3 | *J. Name.*, 2012, **00**, 1-3

This journal is © The Royal Society of Chemistry 20xx

the required energy input can be largely brought down, as demonstrated by the decrease in the thermodynamic cell potential $|E^0|$ from 1.11 V to 0.33 V (Fig. 4b).

To demonstrate the feasibility of the paired electrolysis experimentally, we first performed linear sweep voltammetry (LSV) analysis in the flow cell, with ECH of HMF catalyzed by OD-Ag and ECO of HMF mediated by TEMPO (Fig. 4a). The results for ECH-ECO paired electrolysis (Fig. 4c) exhibited a remarkable decrease in cell voltage compared to the ECH-OER system: 1.5 V vs. 2.0 V at 5 mA; 29.1 mA vs. 15.6 mA at 2.5 V.

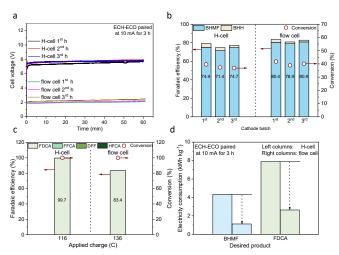


Fig. 5. Comparison of ECH-ECO paired electrolysis in the flow cell and H-type cell at 10 mA. (a) Cell voltage profiles for three consecutive 1-hour electrolysis in the H-type cell and flow cell. (b)–(c) Faradaic efficiency and HMF conversion for cathodic and anodic reactions in the H-type cell (left columns) and flow cell (right columns). (d) Comparison of electricity consumption for BHMF and FDCA production different cell configurations. The catholyte was 20 ml of 0.5 M borate buffer (pH 9.2) with 20 mM HMF, and the anolyte was 20 ml of 0.5 M borate buffer (pH 9.2) with 10 mM HMF and 7.5 mM TEMPO. The applied charge for H-type cell test was 116 C, corresponding to the theoretical charge required for 100% conversion of HMF to FDCA. For the flow cell, 136 C was applied in order to achieve ~100% conversion to FDCA. Fresh catholyte was replaced every hour during tests. More details and additional data can be found in Table S3–S6.

To conduct bulk electrolysis in the ECH-ECO paired system, we first confirmed the facile kinetics and high HMF-to-FDCA selectivity mediated by TEMPO in the H-type cell. As shown in Table S2, both constant-potential (in the range of 0.4–0.8 $V_{Ag/AgCl}$) and constant-current measurements (at 10 mA) achieved ~100% HMF conversion with ~100% selectivity and 90+% FE to FDCA.

The ECH-ECO paired electrolysis was then conducted in different cell configurations with ECH on OD-Ag and ECO mediated by TEMPO as the cathodic and anodic reaction, respectively. A schematic illustration of the flow cell configuration is shown in Fig. S5. A substantial decrease in steady-state cell voltage from ~7.5 V to ~2.0 V was observed when the electrolysis was conducted in the flow cell compared to the H-type cell (Fig. 5a), at the constant current of 10 mA. The reduction in voltage is in line with the decrease in the measured resistance between the cathode and anode from 483.2 Ω for the H-type cell to 39.3 Ω for the flow cell (Table S7). No considerable performance drop was observed in three consecutive 1-hour measurements.

Furthermore, the FE of BHMF was well maintained at $^{\sim}80\%$ in the flow cell, slightly higher than the results in the H-type cell (Fig. 5b). The anodic FE was marginally lower in the flow cell compared to the

H-type cell, as more charge (136 C) than the theoretical value (116 C) was required to fully convert HMF to FDCA (Fig 5c). The additional charge consumption, presumably due to the side reaction OER, could be attributed to the imprecise control of the anodic potential. Alternatively, by controlling the applied potential between the reference electrode and anode at 0.6 V (which was selected due to the high performance of HMF-to-FDCA in the range of 0.4–0.8 $V_{Ag/AgCI}$ from the H-type cell measurements) (Fig. S6), the FE of HMF to FDCA was improved to 92.7% (Fig. 6b). However, a decrease in the FE of BHMF on the cathode was observed as the potential between the

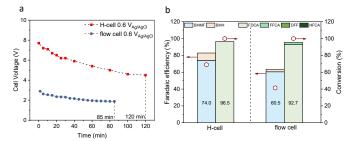


Fig. 6. ECH-ECO paired electrolysis in the three-electrode flow cell at a constant potential of 0.6 V between the reference electrode and anode. (a) Cell voltage profiles for ECH-ECO paired electrolysis in the H-type cell and flow cell at a constant potential of $0.6 \, \rm V_{Ag/AgCI}$ between the reference electrode and anode. The cell voltage was measured by a multimeter. The catholyte was 20 ml of 0.5 M borate buffer (pH 9.2) with 20 mM HMF, and the anolyte was 20 ml of 0.5 M borate buffer (pH 9.2) with 5 mM HMF and 7.5 mM TEMPO. The applied charge was the 57.9 C, corresponding to the theoretical charge required for 100% conversion of HMF to FDCA. More details and additional data can be found in Table S8–S9.

cathode and reference electrode was no longer constant. Further optimization is needed to tackle the challenge of simultaneously controlling the applied potentials on both cathode and anode within the desirable range, thereby maximizing the overall FE.

Nevertheless, a combined FE of over 160% was still attained in our flow reactor to desired BHMF and FDCA. The selectivity to BHMF and FDCA were close to 90% and 100% on the cathode and anode, respectively (Table S3–S6). The electricity consumption (unit: kWh kg $^{-1}$, normalized to the mass of product) to the desired products is shown in Fig. 5d. Compared to the H-type cell, an over three-fold increase was obtained in the flow cell to produce BHMF and FDCA. The cell energy efficiency (ε) as a function of cell voltage was also calculated (detailed in Table S1), which is 24.5% for the flow cell, exhibiting an over four-fold increase compared to the H-type cell (5.7%).

The versatility of the paired electrolysis was demonstrated by extending the substrate to furfural, another bio-derived chemical with an industrial production capacity of 400 ktons per year.^{35, 36} By pairing ECH of furfural-to-furfuryl alcohol (FA) on Pb foil with ECO of furfural-to-furoic acid mediated by TEMPO, a total FE of 177% (90.6% to FA and 87.2% to 2-furoic acid) was obtained (Fig. S7 and Table S10–11). In addition, the superior performance and excellent flexibility of our flow cell for paired electrolysis have approached or outperformed many state-of-the-art reaction systems, as detailed comparison is shown in Table S12.

Journal Name ARTICLE

ECH-HOR paired electrolysis in the flow cell

To further reduce the cell voltage, we performed ECH-HOR paired electrolysis with HMF reduction as the cathodic reaction and HOR as the anodic reaction (Fig. 7a). OD-Ag and Pt/C-coated carbon paper were used as the cathode and anode, respectively. As shown in the LSV curve (Fig. 7b), only 0.85 V of total cell voltage is required to attain a current of 10 mA. The selectivity to BHMF was as high as 82.3% at the cell voltage of 0.90 V (Fig. 7c). The ECH-HOR paired electrolysis offers another sustainable pathway for BHMF production with low energy cost. The continuous fall of renewable electricity prices, along with further development of electrolyzers for $\rm H_2$ generation and conversion of bio-derived chemicals, warrants the potential feasibility of such electrochemical process in the future.

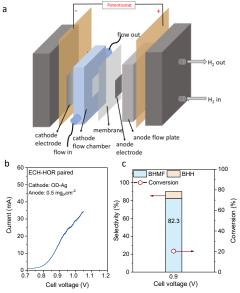


Fig 7. ECH of HMF paired with hydrogen oxidation reaction (HOR) in the flow cell. (a) Schematic illustration of the flow cell for ECH-HOR paired electrolysis. (b) Linear sweep voltammogram of paired electrolysis with a scan rate of 5 mV s⁻¹. (c) Product selectivity and HMF conversion on OD-Ag at the cell voltage of 0.9 V for half-hour electrolysis. The cathode was OD-Ag and the anode was a Pt/C-loaded carbon paper (0.5 mg_{Pt} cm⁻²). The catholyte was 20 ml of 0.5 M borate buffer (pH 9.2) with 20 mM HMF. The flow rate of H₂ was 100 ml min⁻¹.

Conclusions

High selectivity (90%+) of HMF reduction to BHMF was observed on OD-Ag, which significantly outperformed Ag foil. Such performance can be maintained in a wide range of potential (-1.05 V to -1.35 V) and is stable for prolonged electrolysis. Substitution of the anodic OER by TEMPO-mediated HMF oxidation notably lowered the overall cell voltage, which was further reduced to 2.0 V (at 10 mA) in a flow cell. Such ECH-ECO paired electrolysis in the flow cell offered a combined FE of 163% to the valuable products (BHMF and FDCA) and demonstrated an over four-fold increase in energy efficiency. Using HOR as an alternative anodic reaction, the cell voltage was further reduced to 0.85 V, offering a potential renewable substitute of thermocatalytic hydrogenation of bio-based chemicals. The efficient conversion of HMF, alongside the concept of paired electrolysis developed in the present study, will open up sustainable, economically-viable, and environmental-benign routes of harnessing renewable energy for efficient utilization of biomass-derived feedstocks for distributed manufacturing of valuable chemicals.

Experimental section

Chemicals and Materials

Sodium hydroxide (97%), potassium hydroxide (85%), furfural (99%), furfural alcohol (FA, 98%), sodium sulfate (99%), 5-(hydroxymethyl)furfural (HMF, 99%), TEMPO[2,2,6,6tetramethylpiperidin-1-yl)oxyl] (98%), 2-furoic acid (98%), 2,5-97%), furandicarboxylic acid (FDCA, 5-hydroxymethyl-2furancarboxylic acid (HFCA, 99%), and 2,5-diformylfuran (DFF, 97%) were purchased from Sigma-Aldrich. Acetonitrile (CH3CN, HPLC grade), platinum foil (0.025 mm thick, 99.9%), 2-propanol (99.9%), and boric acid (≥99%) were purchased from Fisher Scientific. 2,5-Bis(hydroxymethyl)furan (BHMF, 98%) was purchased from Ark Pharm, Inc. 5-Formyl-2-furoic acid (FFCA, 99%) was purchased from TCI. Silver foil (0.5 mm thick, 99.9985%) was purchased from Alfa Aesar. Teflon (0.002-inch thickness), silicon (0.01-inch thickness) gaskets, Nafion membrane, Toray carbon paper 030, and plain carbon cloth were purchased from the Fuel Cell Store. 40 wt.% Pt on Vulcan XC-72 (Pt/C) was purchased from Premetek. A201 anion exchange membrane was purchased from Tokuyama Corp. H₂ calibration gases (10 ppm, 100 ppm, 1,000 ppm, 5,000 ppm, 10,000 ppm, balance helium) were purchased from Cal Gas Direct. Deionized (DI) water (18.2 MΩ cm, Barnstead™ E-Pure™) was used for all experiments in this work. All electrochemical tests were performed by a Biologic SP-300 potentiostat with a ±2 A/±30 V booster.

Preparation of the working electrode

OD-Ag was prepared in a standard three-electrode system by a modified electrochemical square-wave-voltammetry (SWV) method. The properties of polished and cleaned Ag foil was immersed in a 0.2 M NaOH electrolyte as the working electrode. Ag/AgCl (saturated KCl, Pine Research) and platinum foil served as the reference electrode and counter electrode, respectively. Cyclic voltammetry (CV) was applied from 0 to 1.2 $V_{Ag/AgCl}$ with a scan rate of 20 mV s⁻¹. A symmetric square-wave pulse potential was then applied on Ag foil from 0 to 1.0 $V_{Ag/AgCl}$ at the frequency of 500 Hz for 3 h with both positive and negative scans. Subsequently, a constant potential (–1.3 $V_{Ag/AgCl}$) was applied for 10 min to obtain OD-Ag.

To prepare Pt/C on carbon paper, catalyst ink was prepared by dispersing Pt/C in a mixture of DI water and 2-propanol (1:2 volume ratio) with added AS-4 ionomer by ultrasonication. The mass ratio of Pt/C and AS-4 ionomer was 4:1. The ink was then airbrushed onto the carbon paper to a final loading of around 0.5 mg_{Pt} cm⁻².

Electrochemical measurements in the H-type cell

To perform ECH in an H-type cell, a three-electrode configuration was set up with Ag/AgCl as the reference electrode and Pt foil as the counter electrode. The geometric area of the working electrode was 2 cm². Anode and cathode compartments were separated by a Tokuyama A201 anion-exchange membrane. The electrolyte was prepared in 0.5 M borate buffer solution (pH 9.2), and 20 ml of the electrolyte was used in each compartment. The resistance between the working and reference electrodes was determined by potentiostatic electrochemical impedance spectroscopy, and 90% *iR*-compensation was applied for all measurements.

Cyclic voltammetry (CV), linear sweep voltammetry (LSV), and chronoamperometry (CA) tests were conducted under a constant Ar flow through the catholyte for deaeration and on-line analysis of evolved H_2 by gas chromatography (GC). CV and LSV were carried out without magnetic stirring. During CA tests, the catholyte and anolyte

5 | *J. Name.*, 2012, **00**, 1-3

This journal is © The Royal Society of Chemistry 20xx

were stirred by PTFE-coated magnetic bars (20 \times 6 mm, Chemglass Life Sciences) at 350 r.p.m.

ECO (HMF oxidation) and paired electrolysis were performed in a similar configuration. A piece of carbon cloth (2 cm²) was used for TEMPO-mediated HMF oxidation. The concentration of TEMPO in the anolyte was 7.5 mM.

Electrochemical measurements in the flow cell

Flow cell electrolysis was performed by an in-house built system, which contains stainless-steel endplates, gold current collectors, PTFE and silicone gaskets, a PTFE flow chamber (cathode) with an Ag/AgCl reference electrode, an anion exchange membrane (Tokuyama A201), and a graphite flow-field plate (anode). The geometric area of the cathode and anode were 2 and 5 cm², respectively. The catholyte and anolyte (both 20 ml) were circulated by a peristaltic pump (Masterflex® L/S®) at 50 ml min⁻¹.

Quantification methods

Liquid products were analyzed by High-Performance Liquid Chromatography (HPLC, Agilent Technologies, 1260 Infinity II LC System) equipped with a variable wavelength detector (Agilent 1260 Infinity Variable Wavelength Detector VL). The wavelength of 225 nm and 260 nm was applied to quantify cathodic products (including HMF, BHMF, furfural, FA, and dimers) and anodic (including HMF, FDCA, HFCA, FFCA, and DFF) products, respectively. Detailed HPLC conditions were reported in our previous works. ^{17, 32} For simplicity, two isomers of the dimer product [5.5'bis(hydroxymethyl)hydrofuroin, BHH] are reported together. For the quantification of furfural and 2-furoic acid, same conditions were used for the analysis of HMF oxidation products except that the flow rate of the mobile phase was increased to 1.1 ml min⁻¹, and the retention time was around 28.7 min and 18.6 min for furfural and 2furoic acid, respectively.

 $\rm H_2$ was quantified by on-line GC (SRI Instrument 8610C MG#3) equipped with HaySep D and MolSieve 5 Å columns and a thermal conductivity detector. The calibration curve was established by analyzing the standard calibration gases with different concentrations (10–10,000 ppm).

The GC program was started 2 min after the electrolysis was initiated, and a 6-min programmed cycle (including a 4-min running period and a 2-min cooling period) was repeated throughout the measurement.

The rate of H_2 generation (r, mol s⁻¹) for each cycle was calculated by Eqn. 4:

$$r = c \times 10^{-6} \times [\rho \dot{V} \times 10^{-6}/(RT)]$$
 (4)

Where c is the H₂ concentration (ppm); \dot{V} is the volumetric flow rate of the inlet gas (12.5 mL min⁻¹); p is the ambient pressure (p = 1.013 × 10⁵ Pa); R is the gas constant (R = 8.314 J mol⁻¹ K⁻¹); T is the room temperature (293.15 K). The total amount of H₂ production (mol) was calculated by integrating the plot of H₂ production rate (mol s⁻¹) vs. reaction time (s) with polynomial curve fitting.

Materials Characterization

X-ray diffraction (XRD) crystallography was collected with a Siemens D500 diffractometer operated with a Cu K_{α} source (λ = 1.5418 Å) at 45 kV and 30 mA and equipped with a diffracted beam monochromator (carbon). X-ray photoelectron spectroscopy (XPS) was collected with a Kratos Amicus/ESCA 3400 X-ray photoelectron

spectrometer with Mg K $_{\alpha}$ X-ray (1,253.7 eV). All XPS spectra were calibrated with the C 1s peak at 284.8 eV. Scanning Electron Microscopy-Energy Dispersive X-ray Spectroscopy (SEM-EDS) was conducted on a field-emission scanning electron microscope (FEI Quanta-250) equipped with a light-element X-ray detector and an Oxford Aztec energy-dispersive X-ray analysis system.

Calculations

The conversion (X) and product selectivity (S_i) were calculated by Eqs. 5–6:

$$X = (n_0 - n)/n_0 \times 100\%$$
 (5)

$$S_i = n_i/(n_0 - n) \times 100\%$$
 (6)

Where n_0 is initial moles of HMF; n is the moles of HMF after electrolysis; n_i is the moles of product i (BHMF, BHH, DMF, HFCA, DFF, FFCA, and FDCA).

The FE of product i (FE $_i$) was calculated by Eqn. 7:

$$FE_i = (n_i z_i F)/Q \times 100\%$$
 (7)

Where z_i is the number of electrons transferred for one product molecule; F is the Faraday constant (96,485 C mol⁻¹); Q is the total charge passed through the electrolytic cell.

Energy efficiency (ε) as a function of cell voltage ($V_{\rm cell}$) was calculated by Eqn. 8:

$$\varepsilon = |E_{\text{cell}}|/V$$

=
$$|FE_{BHMF} \times E_{HMF/BHMF} - FE_{FDCA} \times E_{HMF/FDCA}|/V \times 200\%$$
 (8)

Where $E_{\rm HMF/BHMF}$ and $E_{\rm HMF/FDCA}$ denoted the thermodynamic reduction potentials for HMF-to-BHMF and FDCA-to-HMF reactions, respectively, under the testing conditions (pH 9.2). Detailed calculations are shown in the Supporting Information.

Author contributions

W.L. and E.W.C. conceived and supervised the project. H.L., T.L., and Y.C. performed all electrochemical measurements and physical characterization. All authors discussed the results and contributed to the manuscript writing.

Conflicts of interest

The authors declare no conflict of interest.

Acknowledgments

This work was supported by the National Science Foundation under grant no. CBET-1947435. We thank Drs. Dapeng Jing, Curtis L. Mosher, and Warren E. Straszheim for their assistance with XPS, AFM, and SEM measurements. W. Li is grateful to his Herbert L. Stiles Faculty Fellowship.


References

- 1. T. Mai, M. M. Hand, S. F. Baldwin, R. H. Wiser, G. L. Brinkman, P. Denholm, D. J. Arent, G. Porro, D. Sandor and D. J. Hostick, *IEEE Transactions on Sustainable Energy*, 2013, **5**, 372–378.
- 2. M. Bui, C. S. Adjiman, A. Bardow, E. J. Anthony, A. Boston, S. Brown, P. S. Fennell, S. Fuss, A. Galindo and L. A. Hackett, *Energy Environ. Sci.*, 2018, **11**, 1062–1176.
- E. J. Horn, B. R. Rosen and P. S. Baran, ACS Cent. Sci., 2016, 2, 302–308.
- 4. S. Verma, S. Lu and P. J. Kenis, Nat. Energy, 2019, 4, 466–474.
- 5. J. G. Ibañez Cornejo, B. A. Frontana Uribe and R. Vasquez Medrano, *J. Mex. Chem. Soc.* 2016, **60**, 247–260.
- 6. J. Na, B. Seo, J. Kim, C. W. Lee, H. Lee, Y. J. Hwang, B. K. Min, D. K. Lee, H.-S. Oh and U. Lee, *Nat. Commun.*, 2019, **10**, 1–13.

Journal Name ARTICLE

- 7. M. J. Llorente, B. H. Nguyen, C. P. Kubiak and K. D. Moeller, *J. Am. Chem. Soc.*, 2016, **138**, 15110–15113.
- 8. M. A. Bajada, S. Roy, J. Warnan, K. Abdiaziz, A. Wagner, M. M. Roessler and E. Reisner, *Angew. Chem. Int. Ed.* 2020, **59**, 15633–156419.
- S. Choi, M. Balamurugan, K.-G. Lee, K. H. Cho, S. Park, H. Seo and K. T. Nam, *J. Phys. Chem. Lett.*, 2020, **11**, 2941–2948.
- 10. Q. Qin, T. Heil, J. Schmidt, M. Schmallegger, G. Gescheidt, M. Antonietti and M. Oschatz, *ACS Appl. Energy Mater.*, 2019, **2**, 8359–8365.
- 11. X. Wei, Y. Li, L. Chen and J. Shi, *Angew. Chem. Int. Ed.* 2021, **60**, 3148–3155.
- 12. X. V. Medvedeva, J. J. Medvedev, S. W. Tatarchuk, R. M. Choueiri and A. Klinkova, *Green Chem.* 2020, **22**, 4456–4462
- 13. R. S. Sherbo, R. S. Delima, V. A. Chiykowski, B. P. MacLeod and C. P. Berlinguette, *Nat. Catal.*, 2018, **1**, 501–507.
- 14. P. Zhang, X. Sheng, X. Chen, Z. Fang, J. Jiang, M. Wang, F. Li, L. Fan, Y. Ren and B. Zhang, *Angew. Chem. Int. Ed.*, 2019, **58**, 9155–9159.
 15. S. Li, X. Sun, Z. Yao, X. Zhong, Y. Cao, Y. Liang, Z. Wei, S. Deng, G. Zhuang and X. Li, *Adv. Funct. Mater.*, 2019, **29**, 1904780.
- 16. X. Zhang, M. Han, G. Liu, G. Wang, Y. Zhang, H. Zhang and H. Zhao, *Appl. Catal. B.*, 2019, **244**, 899–908.
- 17. X. H. Chadderdon, D. J. Chadderdon, T. Pfennig, B. H. Shanks and W. Li, *Green Chem.*, 2019, **21**, 6210–6219.
- 18. W. A. Smith, T. Burdyny, D. A. Vermaas and H. Geerlings, *Joule*, 2019, **3**, 1822–1834.
- 19. J. J. Bozell and G. R. Petersen, *Green Chem.*, 2010, **12**, 539–554.
- 20. J. N. Chheda, Y. Román-Leshkov and J. A. Dumesic, *Green Chem.*, 2007, **9**, 342–350.
- 21. C. Moreau, M. N. Belgacem and A. Gandini, *Top. Catal.*, 2004, **27**, 11–30.
- 22. S. Rajendran, R. Raghunathan, I. Hevus, R. Krishnan, A. Ugrinov, M. P. Sibi, D. C. Webster and J. Sivaguru, *Angew. Chem.*, 2015, **127**, 1175–1179.
- 23. J. J. Roylance, T. W. Kim and K.-S. Choi, *ACS Catal.*, 2016, **6**, 1840–1847.
- 24. H. G. Cha and K.-S. Choi, Nat. Chem., 2015, 7, 328-333.
- 25. W.-J. Liu, L. Dang, Z. Xu, H.-Q. Yu, S. Jin and G. W. Huber, *ACS Catal.*, 2018, **8**, 5533–5541.
- 26. N. Zhang, Y. Zou, L. Tao, W. Chen, L. Zhou, Z. Liu, B. Zhou, G. Huang, H. Lin and S. Wang, *Angew. Chem.*, 2019, **131**, 16042–16050. 27. B. You, X. Liu, N. Jiang and Y. Sun, *J. Am. Chem. Soc.*, 2016, **138**, 13639–13646.
- 28. N. Jiang, B. You, R. Boonstra, I. M. Terrero Rodriguez and Y. Sun, *ACS Energy Lett.*, 2016, **1**, 386–390.
- 29. M. Hans, S. Mathews, F. Mücklich and M. Solioz, *Biointerphases*, 2016, **11**, 018902.
- 30. J. E. Pander, D. Ren, Y. Huang, N. W. X. Loo, S. H. L. Hong and B. S. Yeo, *ChemElectroChem*, 2018, **5**, 219–237.
- 31.N. Tian, Z.-Y. Zhou, N.-F. Yu, L.-Y. Wang and S.-G. Sun, *J. Am. Chem. Soc.*, 2010, **132**, 7580–7581.
- 32. X. H. Chadderdon, D. J. Chadderdon, J. E. Matthiesen, Y. Qiu, J. M. Carraher, J.-P. Tessonnier and W. Li, *J. Am. Chem. Soc.*, 2017, **139**, 14120–14128.
- 33. E. Andrews, J. A. Lopez-Ruiz, J. D. Egbert, K. Koh, U. Sanyal, M. Song, D. Li, A. J. Karkamkar, M. A. Derewinski and J. Holladay, *ACS Sustain. Chem. Eng.*, 2020, **8**, 4407–4418.
- 34. J. Anibal and B. Xu, ACS Catal., 2020, 10, 11643-11653.
- 35. R. Mariscal, P. Maireles-Torres, M. Ojeda, I. Sádaba and M. L. Granados, *Energy Environ. Sci.*, 2016, **9**, 1144–1189.
- 36. A. Banerjee, G. R. Dick, T. Yoshino and M. W. Kanan, *Nature*, 2016, **531**, 215–219.
- 37. M. Ma, B. J. Trzesniewski, J. Xie and W. A. Smith, *Angew. Chem. Int. Ed.*, 2016, **55**, 9748–9752.

Table of Contents

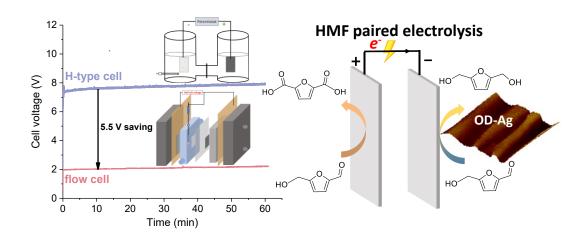

Text:

Paired electrolysis of HMF in a flow cell markedly reduces cell voltage and realizes co-production of BHMF and FDCA.