

Nanoscale Advances

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: Y. Song, P. C. Lan, K. Martin and S. Ma, *Nanoscale Adv.*, 2021, DOI: 10.1039/D1NA00479D.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

ARTICLE

Rational Design of Bifunctional Conjugated Microporous Polymers

Yanpei Song,^a Pui Ching Lan,^a Kyle Martin^a and Shengqian Ma^{*a}Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

ABSTRACT: Conjugated microporous polymers (CMPs) are an emerging class of porous organic polymers that combine π -conjugated skeletons with permanent micropores. Since their first report in 2007, the enormous exploration of linkage types, building units, and synthetic methods for CMPs have facilitated their potential applications in various areas, from gas separations to energy storage. Owing to their unique construction, CMPs offer the opportunity for the precise design of conjugated skeletons and pore environment engineering, which allow the construction of functional porous materials at the molecular level. The capability to chemically alter CMPs to targeted applications allows for the fine adaptation of functionalities for the ever changing environments and necessities. Bifunctional CMPs are a branch of functionalized CMPs that have caught interest of researchers because of their inherent synergistic systems that can expand their applications and optimize their performance. This review attempts to discuss the rational design and synthesis for bifunctional CMPs and summarize their advanced applications. To conclude, our own perspective on the research prospect of this type of material is outlined.

1. Introduction

Materials bearing permanent porosities are considered porous materials, which have drawn wide attention as an attractive platform for their advanced applications in various fields of science and technology. Porosity, however, is not a new concept that has long existed in nature such as the cavities of charcoal in structure. Synthetic porous materials which also possess permanent porosities constantly attract scientists' attention to the discovery for their potential applications due to their feasible functionalization. In the past several decades, a variety of synthetic porous materials have emerged and resulted in the explosion of material design. Zeolites and mesoporous silicates are traditional porous materials with inorganic open frameworks which are still widely used in industrial production in modern times.¹⁻⁴ In addition, another type of prevalent inorganic containing porous materials is metal-organic frameworks (MOFs) or porous coordination polymers (PCPs) representing one of the most attractive classes of porous materials nowadays.⁵⁻⁹ As a result of the rapid development of module construction, MOFs held together by coordination bonds can be connected in a predictable manner. This then allows for the feasibility to manipulate the functional units and spatial structures of the framework thereby allowing control over the internal surface engineering and functionalization of MOFs.¹⁰⁻¹³ In sharp contrast to the inorganic or inorganic-hybrid porous materials, there is also a collection of advanced organic materials with permanent nano-porosities which are constructed by the infinite connection of covalent bonds between organic units, and these materials are classified as porous organic materials.

In the past two decades, covalent organic frameworks (COFs),¹⁴⁻¹⁸ covalent triazine frameworks (CTFs),¹⁹⁻²³ porous organic polymers (POPs),²⁴⁻²⁷ hyper crosslinked polymers (HCPs),²⁸⁻³¹ porous aromatic frameworks (PAFs)³²⁻³⁵ and conjugated microporous polymers (CMPs)³⁶⁻³⁹ have been introduced, and most of them are amorphous and disordered networks except for COFs and a small amount of CTFs. These porous organic materials possess various structural features and linking knots, they, however, are all constructed by light elements with high porosity, excellent stability, and facile functionalization. Among these porous organic materials, CMPs are the unique ones because of their extended π -conjugated skeletons which build the porous 3D networks of CMPs. Based on this concept, CTFs are also able to be considered as a subclass of CMPs because of their microporous properties and extended π -conjugation in structure, although there are many differences in the construction between them and traditional CMPs.

The initial effort to construct CMPs was made by Cooper and co-workers when they reported the first three CMP networks.⁴⁰ To achieve the π -conjugated skeletons, these CMPs were synthesized via palladium-catalyzed Sonogashira-Hagihara cross-coupling to ensure that the network was based on a 1,3,5-substituted benzene node connected by rigid phenyleneethynylene struts. The network CMP-1 was obtained from the cross-coupling of 1,3,5-triethynylbenzene and 1,4-diiodobenzene representing an amorphous 3D structure. CMP-1 exhibited microporous property, as revealed by the N₂ sorption isotherms collected at 77 K, with a Brunauer-Emmett-Teller (BET) surface area of 834 m² g⁻¹. Other CMPs, CMP-2, and CMP-3, which are also based on the integration of C3+C2 topological units into CMPs reveal similar 3D structures as CMP-1 with the BET surface areas of 634 and 552 m² g⁻¹, respectively. Cooper's group also was the first to synthesize a soluble CMP network in 2012 via the introduction of tert-butyl-functionalized groups to the skeleton to obtain the hyperbranched CMPs, and thus

^a Department of Chemistry, University of North Texas, 1508 W Mulberry St, Denton, TX 76201, USA. E-mail: shengqian.ma@unt.edu



handling the CMP in a state other than solid.⁴¹ The resultant CMP could dissolve in specific solvent and then cast as thin films, demonstrating the promising application in the separation of gases. Later, Patra⁴² and Hu⁴³ et al. built upon this, reporting another two examples of the casting of thin films from soluble CMPs and their applications in light emission and fluorescence detection, respectively. These successful attempts stimulate the growth of CMP materials from the building block design to the synthetic methods. Due to the diversity of chemical reactions, numerous coupling units are designed for the application of interest, which also expand the synthetic reactions for the construction of CMP networks, including Sonogashira-Hagihara reaction,⁴⁴ Suzuki cross-coupling reaction,^{45,46} Yamamoto reaction,⁴⁷ Heck reaction,⁴⁸ Friedel-Crafts reaction,^{49,50} phenazine ring fusion reaction,^{51,52} oxidative coupling reaction,⁵³ Schiff-base reaction^{54,55} and cyclotrimerization reaction (Fig. 1).^{56,57}

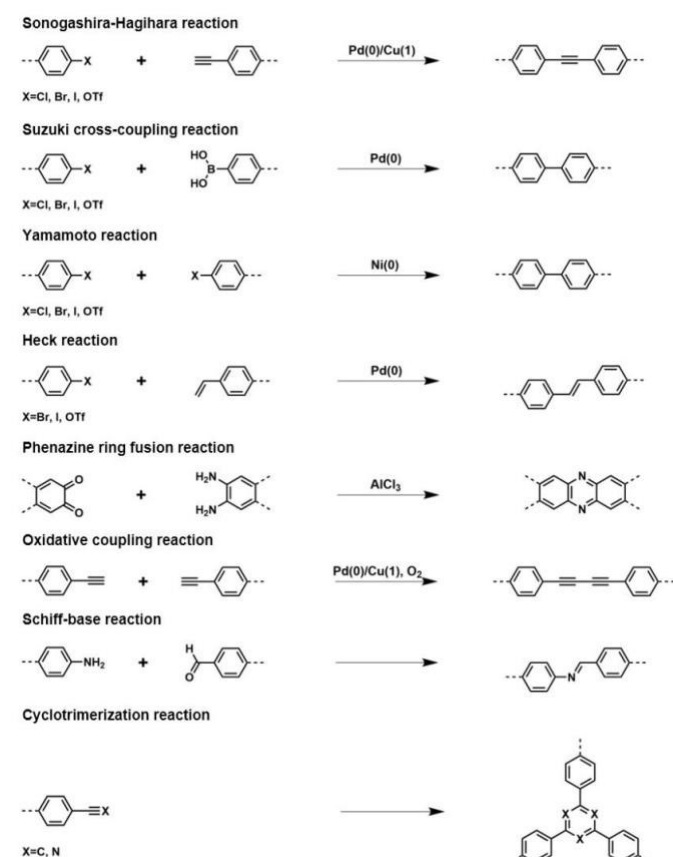


Fig. 1 Schematic representation of reactions for the synthesis of CMPs.

2. Design and Synthesis of Bifunctional CMPs

CMPs with their unique π -conjugated skeletons and permanent micropores in structure demonstrate the great potential in advanced applications which can be designed at the molecular level and constructed according to researchers' intention. With the advent of CMPs, they have been applied for gas storage and separation due to their inherent advantages such as high surface areas and rigid π -conjugated structures.⁵⁸⁻⁶² Functionalizing CMPs beyond their intrinsic properties represents a foreseeable approach to addressing critical challenges such as heterogeneous catalysis,⁶³⁻⁶⁷

photocatalysis,⁶⁵⁻⁶⁷ light emittance,⁶⁸⁻⁷⁰ environmental remediation,⁷¹⁻⁷⁴ chemical sensing,⁷⁵⁻⁷⁸ and energy storage.⁷⁹⁻⁸⁷ In addition, bifunctional CMPs with multiple active sites or functionalities can strengthen their performance with the close cooperation of diverse assistant groups and improve the issue of low efficiency in single-functional CMPs that may hinder their practical applications. In this section, we review the design and synthesis of bifunctional CMPs with a rational evaluation of these strategies.

2.1 Design principles

The routes to design and synthesize a CMP network are full of challenges, which require researchers to have a careful consideration for the network structures and appropriate methods to include functionalities in CMPs. Generally, the establishment of CMP network is driven by their skeleton architecture or potential application with the well-designed functional groups. Sometimes it is also necessary to address a task with the combination of these factors together. It is well known that the self-condensation of the homo-coupling of single building blocks occurs earlier than that of CMPs such as the first success for the construction of COF-1 which is obtained by the self-condensation of 1,4-benzene diboronic acid with the crystalline structure and permanent porosity.¹⁴ However, the discovery of such porous organic polymers is limited by their confined establishment of skeletons which are merely the infinite duplication of homo-monomers. Thus, an important principle for designing functional CMPs, especially the bifunctional CMP, is that diverse building monomers with two or more active groups are necessary to endow the resultant CMP with accessible functionalities beyond their π -conjugated skeletons. According to this principle, the rational design of monomers and accessible functionalizing methods are indispensable for the consideration of researchers. After the first introduction of the CMP network,⁴⁰ a variety of π units have been reported to be employed to build up CMP networks with enhanced π -conjugation in structure. The resultant CMPs are applied to the π -conjugation favored applications such as photocatalysis,⁶⁸⁻⁷⁰ light emittance,⁷¹⁻⁷³ chemical sensing⁷⁸⁻⁸¹, and energy storage.⁸²⁻⁸⁷ As for the accessible synthesis of monomers, the method of constructing CMPs using Suzuki-Miyaura cross-coupling reaction has to be stated because of its commercial availability for monomers and wide functional group compatibility, which facilitates the development of the family of functional CMPs. The Suzuki-Miyaura cross-coupling reaction was first reported in 1979 as an outstanding method to link aryl groups,^{88,89} and the introduction of Suzuki-Miyaura cross-coupling reaction to the construction of CMP network accelerates the discovery of diverse advanced applications of CMPs with various choices of functionalized building units.

To obtain the specific functionalities in CMP networks, the appropriate methods for inducing functional groups to the skeleton of CMPs are significant. The most commonly used methods are *de novo* synthesis for building monomers and post-synthetic modification for resultant backbone, which are also widely utilized in the functionalization of other porous materials such as MOFs^{90,91} and COFs.^{92,93} Both methods exhibit effective functionalization of CMPs but employ different strategies to attach the functional groups or active sites to the networks of CMP. *De novo* synthesis is a bottom-up strategy which ensures the highest degree of grafting in the



resultant CMPs according to the design principles for the target applications, whereas post-synthetic modification tailors a CMP network after the CMP network has already been synthesized. Even though, post-synthetic modification is a hugely popular method to functionalize CMPs which provides a versatile tool to create a variation of the pristine CMPs with identical spatial structures. This modification also referred to as post-synthetic functionalization, allows for the diverse functionalities of CMPs, but might bring the unexpected structural collapse of CMPs. Thus, a deliberate consideration for the functionalization of CMPs through post-synthetic modification would be especially important while tailoring the CMP networks without the decrease of structural stability. This method is usually employed when the target CMPs cannot be synthesized via the construction of the functional monomers which are hard obtained from traditional synthesis routes. In summary, both *de novo* synthesis and post-synthetic modification of CMPs offer us the decorating techniques for the tailoring of a CMP network with tailored and anticipated properties, which give these porous organic polymers more advanced applications.

2.2 Synthetic methods

2.2.1 *De novo* synthesis

Due to the great diversity of organic synthesis, the tremendous potential designs of functionalized monomers provide researchers a huge reserve of building blocks for the construction of CMP materials to choose from. With these monomers of interest in hand, the CMPs can be synthesized according to the requirement of researchers with different shapes of the pore space and various functionalization of the pore environment. Utilizing *de novo* synthesis for functionalizing CMPs, a variety of target networks with distinctive active sites have been developed and employed in a range of research fields with challenges.

2.2.1.1 *De novo* synthesis of π units

De novo synthesis is ideal as it ensures the highest degree of grafting in regard to this, promising each monomer unit containing a functional group at least. The first CMPs were synthesized by Sonogashira-Hagihara cross-couplings, and the aryl halides were coupled by the alkyne struts, forming rigid porous structures with the alkyne knots existing in the networks.⁴⁰ On this foundation, a range of monomers containing aryl halides with the specific functional group have been designed and applied to construct CMPs which exhibit enhanced performance in practical applications, such as photocatalysis. To access the goal for improving the performance of photocatalysis in CMPs, Vilela et al. in 2013 reported a series of benzothiadiazole-based CMPs which were synthesized through palladium-catalyzed Sonogashira-Hagihara cross-coupling (Fig.2).⁹⁴ The synthesized CMPs dispersed in DMF were tested to obtain the UV/Vis spectra in comparison to the benzothiadiazole monomer afterward, representing a large bathochromic shift of around 90 nm in this conjugated network. These results indicate the π -conjugated system of the monomer might be enlarged via the poly-coupling reaction. These bifunctional CMPs with enhanced π -conjugated effect were employed to evaluate their photocatalytic activities, exhibiting the obviously improved performance along with the increase of surface areas of these CMPs, although they were constructed by the same block units. The difference in the

photocatalytic performance for these CMPs reveals that the increased contact area between catalysts and reactants is another significant factor for improving photocatalytic efficiency besides the enhanced π -conjugation of CMP materials. Soon after, Cooper et al. reported the synthesis of two dye-based CMPs with prominent photoredox catalysis which were prepared using Rose Bengal dye with 1,4-diethynylbenzene and 1,3,5-triethynylbenzene, respectively as blocking units.⁹⁵ The resultant two CMPs, RB-CMP1 and RB-CMP2, both exhibited high conversions and recyclability in Aza-Henry reactions as photoredox catalysts. Similarly, Han et al. built upon this, demonstrating the EY-POPs which were constructed by the embedding of Eosin Y dye in CMPs via a bottom-up strategy.⁹⁶ Two EY-POPs were obtained, and 1,3,5-triethynylbenzene and tetra(4-ethynylphenyl)methane were respectively used to support Eosin Y dye in the yield π -conjugated networks. These photoactive CMPs reveal high activity and ready recyclability in the Aza-Henry reaction. To sum up, this strategy of improving the synergistic effect of active sites and inherent porosities in CMPs is proved to be effective, which is also employed widely in designing other functional porous materials, such as MOFs⁹⁷ and COFs.^{98,99}

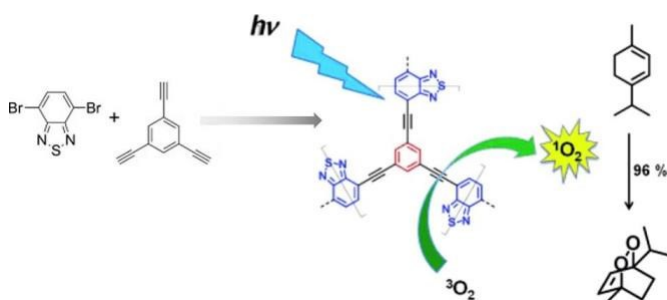


Fig. 2 Synthesis of benzothiadiazole functionalized CMPs. Reproduced with permission.⁹⁴ Copyright 2013, John Wiley and Sons.

2.2.1.2 *De novo* metalation of monomers

The Suzuki-Miyaura cross-coupling reaction was utilized in the construction of CMPs subsequently, which advanced the development of functional CMPs because of its commercial availability of monomers and wide functional group compatibility. This reaction, however, has an inevitable shortcoming: it is oxygen-sensitive, which may result in the production of unexpected by-products and decomposition of Pd(0) catalyst. Therefore, the reaction system should be thoroughly degassed while synthesizing such CMPs.¹⁰⁰ Jiang et al. demonstrated a light-harvesting conjugated microporous polymer named PP-CMP with 3D polyphenylene scaffolds which were synthesized by a Suzuki polycondensation reaction in 2010.¹⁰¹ The success of constructing PP-CMP through Suzuki cross-coupling reaction led to the diversity of π units and the rapid discovery of such type of CMPs. Bhattacharya et al. reported a conjugated donor-acceptor-based bicontinuous microporous networks named Co-MPPy-1, functionalized with a porphyrin unit coordinating with Co(II) ions.¹⁰² Co-MPPy-1 was obtained by the condensation of 1,3,6,8-tetrakis(4,4,5,5-tetramethyl-1,3,2-dioxaborolan-2-yl)pyrene (TBP) and 5,10,15,20-(tetra-4-bromophenyl)porphyrin cobalt(II) (Por-Br) complex through a Pd-mediated Suzuki C-C cross-coupling reaction with a BET surface area of 501 m² g⁻¹, (Fig.3) exhibiting excellent electrochemical activity towards Oxygen Evolution Reaction (OER). The



electrochemical oxygen evolution for Co-MPPy-1 and MPPy-1 which were treated in the acid solution to remove all metal sites (Co) from the CMP networks was evaluated; Co-MPPy-1 represented superior electrochemical activity comparing with MPPy-1. The remote electronic communication between the cobalt(II) porphyrin (donor) to pyrene (acceptor) combining with the efficient charge transport in Co-MPPy-1 networks results in the enhanced performance for its catalytic activity. Subsequently, Lan et al. nicely demonstrated covalent organic framework nanosheets for highly active electrocatalytic carbon dioxide reduction.¹⁰³ They employed the same strategy to enhance the electrocatalytic CO₂ reduction reaction (CO₂RR) performances of the catalyst. Co-TTCOF, condensed by metalized 5,10,15,20-tetrakis (4-aminophenyl) porphyrato (M-TAPP, M=Co here) and 2,3,6,7-tetra (4-formylphenyl)-tetrathiafulvalene (4-formyl-TTF) via a Schiff-base reaction, was designed to take advantages of the synergistic combination of metalloporphyrin and TTF. This synergistic effect herein plays a vital role in gathering electron donating, electron migration, and electrocatalytic active components in the electrocatalytic CO₂RR. With the high porosity, Co-TTCOF also offers a large electrochemical active surface to transport CO₂. Therefore, the appropriate combination of electron donor monomers with electron acceptors might construct intermolecular charge-transfer pathways in the target materials effectively, which could improve the electron transfer efficiency largely, and thereby enhancing the electrocatalytic activity.

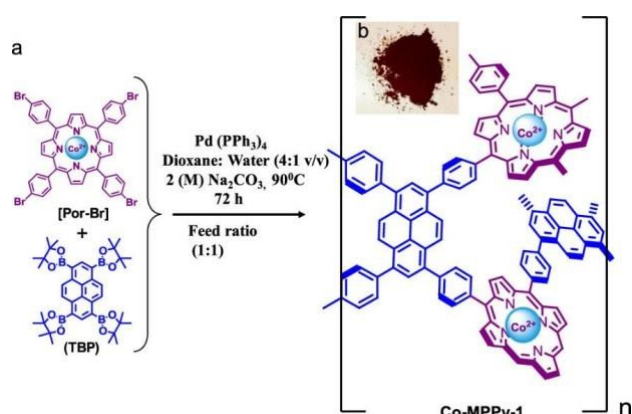


Fig. 3 Synthesis of metalloporphyrin and pyrene-based CMP, Co-MPPy-1. Adapted with permission.¹⁰² Copyright 2019, American Chemical Society.

The Salen unit with its unique coordination geometry is notable for coordinating a wide variety of metals, which makes it one of the most remarkable ligands in coordination chemistry and catalysis chemistry. Deng et al. illustrated the construction of Salen-based CMP materials which could be functionalized by metals of Co and Al, representing high CO₂ uptake ability and effective conversion of CO₂ to propylene carbonate (Fig.4).¹⁰⁴ To obtain Co-CMP, the dibromo-functionalized precursor monomers (Salen-Co) was first synthesized through a complexation reaction of cobalt acetate (Co(OAc)₂) and (R,R)-N,N'-bis(5-bromo-3-tert-butyl-salicylidene)-1,2-cyclohexanediamine (Salen), and then treated with 1,3,5-triethynylbenzene to conjugate monomers via the palladium-catalyzed Sonogashira-Hagihara cross-coupling. While Al-CMP was prepared by the post-modification of Salen-based CMP with Al(OEt)₃, and the resonances of the carbonyl functional groups (-C=O) in Al-

CMP was similar with that in Co-CMP. The resultant CMP, Co-CMP, has a high BET surface area of 965 m² g⁻¹ with a good CO₂ uptake of up to 79.3 mg g⁻¹. What is even more interesting is that the Co-CMP displays excellent catalytic activities at atmospheric pressure and room temperature in the fixation of CO₂ to the useful industrial raw material, propylene carbonate, with tetrabutylammonium bromide (TBAB) as a co-catalyst. The example reveals that the bifunctional CMPs, Co-CMP, and Al-CMP, synthesized with the combination of the advantages of high CO₂ uptake and plenty of active catalytic sites, have a great potential for the practical implementation of CO₂ transformation, and broadening the avenue for designing effective catalysts with bifunctional active sites, as well. Accordingly, Wang et al. reported the first example of a Salen-based COF material. This Salen-COF was obtained by the Schiff-base reaction between 1,3,5-Tris[(5-tert-butyl-3-formyl-4-hydroxyphenyl)ethynyl]benzene and 1,2-ethylenediamine, which constructed and functionalized the Salen moieties in COF in a single step.¹⁰⁵ Benefiting from the unique coordination geometry of Salen units, a family of metallo-Salen-based COFs can be readily prepared via post-synthetic metalation by conducting different metal ions. The Salen unit as one of the most important ligands in coordination chemistry inevitably not only plays a role in the development of functional porous materials but also pushes forward the applications of such materials due to its structural uniqueness.

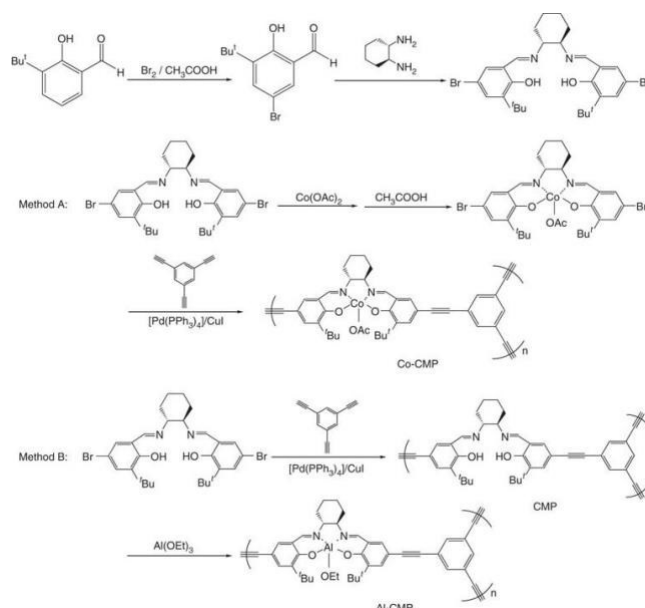


Fig. 4 Synthesis and metalation of Salen-based CMPs, Co-CMP, and Al-CMP. Adapted with permission.¹⁰⁴ Copyright 2013, Nature Publishing Group.

2.2.1.3 De novo synthesis of conjugated nodes

Recently, a range of CMPs named as Aza-CMPs are produced by the phenazine ring fusion, Jiang et al. firstly described the preparation and energy storage behavior of these CMPs. The aza-fused CMPs were prepared by the fusion of 1,2,4,5-benzenetetramine with triquinoyl hydrate in the presence of AlCl₃ at a high temperature in the evacuated ampule and forming 3D ladder CMP networks.¹⁰⁶ This synthesis will require a high reaction temperature, as high as 300-



500 °C, which is uneconomic and environmentally unfriendly. To address this problem, Mateo-Alonso's group developed a mild solvothermal method to obtain Aza-CMPs by refluxing monomers in the mixture with rational ratio of solvent and acetic acid.¹⁰⁷ The Aza-CMPs developed by Jiang's group were evaluated for supercapacitive energy storage which combined the merits of a fused skeleton, dense aza units and well-defined micropores networks, and thus facilitating their electrostatic charge-separation layer formation (Fig.5). This synergistic effect contained in Aza-CMPs reaches the achievement of large capacitance, high energy and power densities, and enabling repetitive energy storage and power supply with an excellent cycle life in CMP materials.

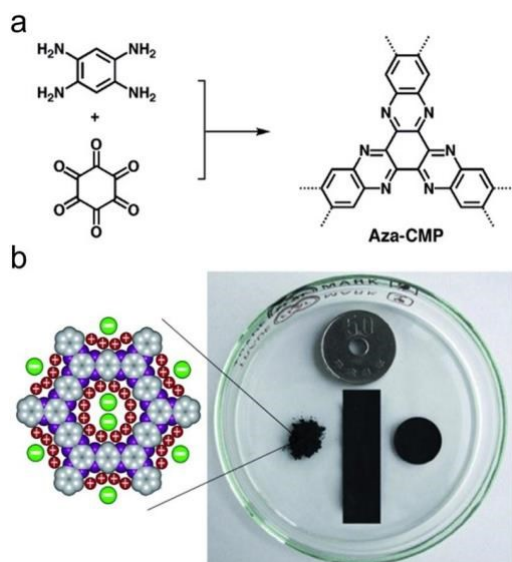


Fig. 5 (a) Synthesis of phenazine-fused Aza-CMP and (b) schematic of enhanced electrolyte ions accumulation on the pore walls. Reproduced with permission.¹⁰⁷ Copyright 2013, John Wiley and Sons.

2.2.2 Post-synthetic modification

In comparison with *de novo* synthesis, post-synthetic modification (PSM) carries out the chemical modification of a CMP network after it has been synthesized, while *de novo* synthesis ensures the highest degree of grafting in the molecule level due to the bottom-up strategy of constructing CMPs. However, with the ease of functionalization of benzene rings that comprise most of the polymers, we can still achieve a very high degree of grafting through post-synthetic modification of CMPs. In 1990, Hoskins and Robson originally proposed the concept of PSM¹⁰⁸ which was introduced to functionalize MOFs by Wang and Cohen until 2007.⁹¹ Subsequently, this strategy has been widely applied to functionalize all porous materials, including CMPs,¹⁰⁹ POPs,¹¹⁰ and COFs,¹¹¹ due to its convenience. PSM has proven to be a general, practical approach for the functionalization of porous materials after years of practical employment.

2.2.2.1 Post-synthetic metalation

The incorporation of active metal sites into the CMP network can greatly introduce the useful chemical functionalities into the pore of CMPs. Some pioneer works have been reported to obtain metal-organic conjugated microporous polymers via the support of metalloporphyrin cores in CMP networks, which significantly expand

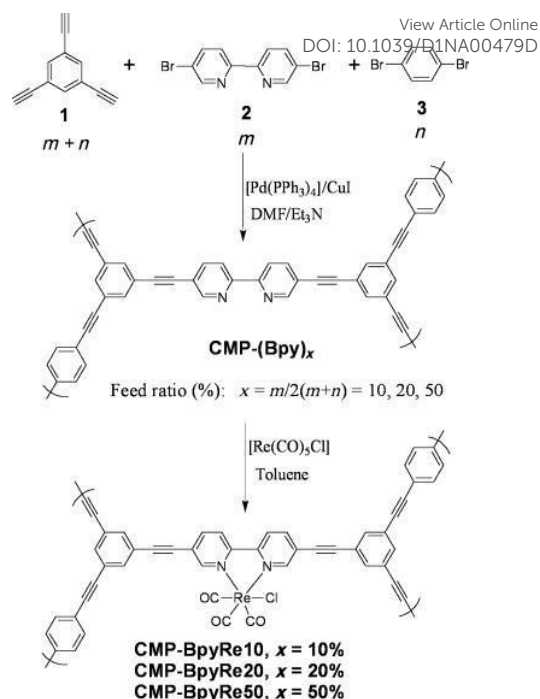


Fig. 6 Synthesis of metal-CMP via post-synthetic metalation. Adapted with permission.¹¹⁴ Copyright 2010, John Wiley and Sons.

the applications of CMPs with the effective combination of chemical and physical properties in the single porous material.¹¹² Cooper et al. described two versatile strategies for constructing metal-organic CMPs (MO-CMPs) without porphyrin-driving monomers (Fig.6).¹¹³ Comparing with the popular MOFs in which the metal or metal cluster serves as the linking node to combine inorganic and organic portions in order to establish the open metal-organic framework. The metal sites in the resultant MO-CMPs are no longer needed to connect multiple organic monomers. Rather they are attached to the surface of the CMP skeleton, therefore, allowing the introduction of active metal sites and a variety of functionalities without breaking the skeleton. Furthermore, the modification of metal sites after the CMP network being synthesized ensures the maintenance of the extended π -conjugation in CMPs. The CMP-(Bpy)_x was prepared by Sonogashira-Hagihara cross-coupling of 1,3,5-triethynylbenzene with 5,5'-dibromo-2,2'-bipyridine and 1,4-dibromobenzene with varying proportions of bipyridines and aromatic groups to manipulate the content of active metal sites in the CMP network. The obtained CMP-(Bpy)_x was treated in the [Re(CO)₅Cl] toluene solution to incorporate Re metal sites, and the success of binding Re to the networks was verified by the FT-IR spectra in comparison with the bare CMP-(Bpy)_x. Given this, Canivet and co-workers described a family of bipyridine-based CMPs with different loading of Ni metal sites, which were explored for the potential in the catalytic performance of benzothiophene C-H arylation; and the results indicate that these Ni-doped CMPs with abundant active sites possess high catalytic activities and wide scope of applicable substrates.¹¹⁴ It is obvious that with the aid of post-synthetic modification, we can tune the metal loading in the CMP network precisely and control its chemically active functionalities in accordance with requirements without the damage of the extended π -conjugation in structure, thereby the high porosity of CMPs retains



ARTICLE

Journal Name

which promises the effective molecule transportation in CMPs after the functionalization.

2.2.2.2 Covalent post-synthetic modification

Apart from the loading of various metal sites in the CMP network to construct bifunctional CMP materials, covalent post-synthetic modification of CMPs is another significant method to alter their chemical and physical properties from the pristine CMPs. Over the past few years, comprehensive research on the post-synthetic modification of porous materials has been carried out, and the so-called "click" chemistry has been widely used to attach the functional groups to the pore surface of porous organic materials, such as Azide-alkyne Huisgen cycloaddition^{115,116} and thiol-yne click chemistry.¹¹⁷ Weber et al. employed CMP-1 as the template to react with varying amounts of thioethanol (C_2SH) or 6-mercaptohexanol (C_6SH) to obtain the resultant CMPs with aliphatic alcohols attached.¹¹⁸ The radical thiol-yne chemistry of CMPs based on the "click" chemistry of the thiol group and the ethynylene units of CMPs would affect the morphology of networks and change the optical properties with different degrees of thiol grafting. While exploring the potential applications of such modified CMPs, Chen et al. reported a range of CMPs that the pristine CMP network was treated with various of thiol-containing groups.¹¹⁹ They first synthesized the CMP network, BTT, with the condensation of 4,7-dibromobenzo[c][1,2,5]thiadiazole and 1,3,5-triethynylbenzene via a Sonogashira-Hagihara cross-coupling polycondensation, which was reacted with the cysteamine in the presence of AIBN in anhydrous DMF at 90 °C for 24 h afterward (Fig. 7). The yielded CMP BTT-SC2NH₂ were evaluated on light-driven hydrogen evolution, showing 27.2 times higher than that of BBT. In order to verify the accessibility of amino-functionalized CMPs via thiol-yne reaction, two more CMPs with enhanced π -conjugation were obtained and treated with cysteamine under the same conditions afterward, named as PB-SC2NH₂ and TB-SC2NH₂, which were synthesized by 1,4-diethynylbenzene with 1,3,6,8-tetrabromopyrene and 1,1,2,2-tetrakis(4-bromophenyl)ethene, respectively. Both as-prepared CMPs-SC2NH₂ represented superior photocatalytic H₂ evolution activity in contrast to that of the pristine CMPs. Additionally, the hydrogen evolution rate (HER) and apparent quantum yield (AQY) at 420 nm of BTT-SC2NH₂ are increased up to 27.2 times and 47.1 times comparing with BTT without attaching the cysteamine. From this fact, it indicates that the incorporation of amino groups in CMP networks not only increases the hydrophilic surface areas of CMPs-SC2NH₂ but also amplifies photogenerated charge separation and lengthens electron lifetime, which results in the improvement of the efficiency for subsequent proton reduction.

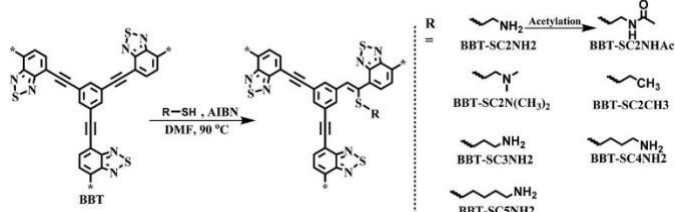


Fig. 7 Synthesis of functionalized BBT via thiol-yne click reaction and its possible structures. Adapted with permission.¹¹⁹ Copyright 2019, Royal Society of Chemistry.

Being similar to the thiol-yne click reaction, the amine groups in CMP can be modified to transfer amines into amides by anhydrides with the maintenance of the microporosity, attaching different alkyl chains in the channel surface of CMPs results in unique functionalities at the pore surface. Cooper et al. demonstrated the synthesis of an amine-functionalized CMP (CMP-1-NH₂) and its potential to convert to amide-functionalized CMP networks (CMP-1-AMD) via the reaction with a series of anhydrides (Fig. 8).¹²⁰ CMP-1-AMD was synthesized by treating CMP-1-NH₂ directly in the various neat anhydrides with stirring for 24 h under 30 °C, offering brown powders after washing with CHCl₃. With the post-synthetic amidation of CMPs, the pore size and the pore surface area of CMPs can be controlled by the length and shape of attached alkyl chains, but also the pore environment can be engineered via the introduction of a wide range of functionalities. The loading of the chirality to porous materials is a challenging task due to the difficulty in designing chiral monomers, CMP-1-AMD network can serve as a platform to obtain chiral CMPs through the reaction of CMP-1-NH₂ and anhydride with chirality. In brief, the incorporation of pore size and pore surface engineering in CMPs paves the avenue for the next-generation bifunctional CMPs.

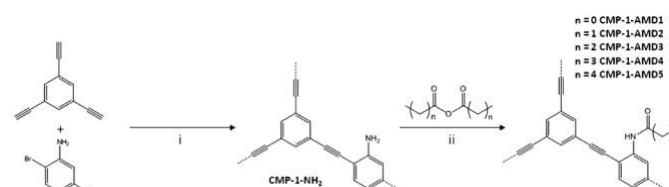


Fig. 8 Synthesis of CMP-1-NH₂ and its post-synthetic modification using anhydrides. Adapted with permission.¹²⁰ Copyright 2014, Elsevier Inc.

The study of CMPs for the adsorption of gases starts at an early stage. The well-defined establishment of the structure for CMPs and nicely selected building composition in CMPs offer us the opportunity to improve their adsorption capacity and selectivity of a specific gas. In order to enhance the CO₂ sorption, Xu et al. introduced metalloporphyrin-based CMPs with the increased electronegativity via post-synthetic fluoride functionalization.¹²¹ The CMP was initially obtained by supporting the core of zinc-porphyrin building block with the mixture of 4,4'-biphenyldiboric acid and (2,5-bis(azidomethyl)-1,4-phenylene)diboric acid via a Suzuki-coupling reaction. The resultant CMPs then were reacted with 1-ethynyl-2,3,4,5,6-pentafluorobenzene to obtain the fluoride functionalized CMPs through a one-step alkyne-azide coupling reaction using CuI as the catalyst. By controlling of the content of azide-containing monomers in CMPs, various target fluoride functionalized networks were synthesized and used to evaluate the CO₂ adsorption capacity. It is interesting that the increment of fluoride content in the skeletons can significantly increase the CO₂ binding ability and thus improving the CO₂ adsorption capacity. Yet the increased functional groups would lower the porosity of networks significantly and impede further contact with CO₂, and then reduce the CO₂ uptake. Therefore, the collaboration of high surface area and enhanced electronegativity of the surface is a promising strategy to discover effective CO₂ adsorbents, providing inspiration for the construction of porous organic materials in the field of gas adsorption.



2.2.2.3 Post-synthetic conversion

Being limited by the complicated synthesis of functional groups in monomers, this type of post-synthetic conversion of functionality is extraordinarily helpful for tailoring the pore environment in CMPs for specific applications. In the report published in 2020, we nicely demonstrated a bifunctional CMP adsorbent for the efficient capture of uranium via post-synthetic conversion of functionality.¹²² The original CMP was designed by the condensation of a single monomer, 1,3,5-triethynylbenzene, which was then treated with malononitrile to obtain the bis -CN group functionalized CMP networks, HCMP-CN. To improve the uranium binding energy and uptake ability, the -CN group was converted to amidoxime group which has a high affinity to uranyl ions (Fig.9). The evaluation for the adsorption of uranium was investigated in the aqueous solutions with the resultant HCMP-AO and showing a much higher adsorption capacity in contrast to that of the original HCMP and HCMP-CN. It indicates that the bis-amidoxime ligands in CMPs contribute to the unique coordination fashion to uranyl ions, suggesting that the synergistic coordination of binding sites can enhance the affinity of chelating groups to the specific ions via the improvement of coordinative binding interactions. The strategy we reported would be a promising method to design adsorbents with outstanding capture ability for diverse ionic contaminants, not merely in the adsorption of uranium.

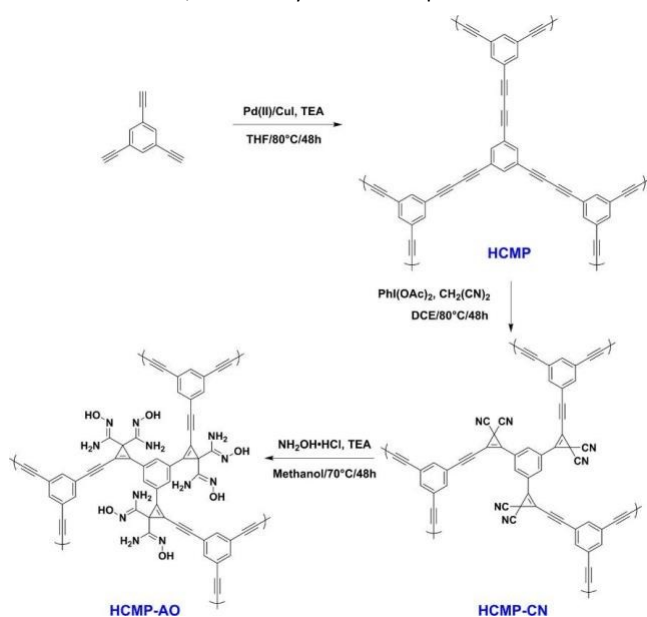


Fig. 9 Synthesis of HCMP-1 functionalized with Bis-amidoxime groups. Adapted with permission.¹²² Copyright 2020, American Chemical Society.

3. Applications of Bifunctional CMPs

3.1 Gas storage and separation

Given the unique structure and high porosity, CMPs were initially evaluated for gas storage and separation. CMPs which are constituted of lightweight elements show great potential for sound gas adsorption capacity and selectivity due to their low density. By means of rational design of building units and synthetic control over structures, the target CMPs can gain improved gravimetric storage

capacity. Hydrogen storage has aroused great interest in the past few decades due to its potential use as clean energy, and CMPs have been investigated for this objective in their early stage. Cooper et al. demonstrated the first application study for CMPs in the field of H₂ storage.⁴⁰ It was found that the network with microporosity had an H₂ adsorption capacity up to 0.99 wt% under the conditions of 77.3 K and 1.13 bar. Another interesting gas storage is the solidification of CH₄ which is an economically attractive fuel, yet the capture and storing of it are full of challenges. HCCP-6 synthesized through the post-synthetic modification from CMP-2 and 1,4-bis(chloromethyl)benzene was evaluated to adsorb CH₄, exhibiting a high CH₄ uptake with a value of 491 mg g⁻¹ at 298 K and 80 bars after the molecular expansion of original CMP-2 networks.¹²³

Besides the storage of fuel gases, the capture of CO₂ which is the main component of greenhouse gases is also widely studied, and a variety of strategies for enhancing CO₂ uptake of CMPs has been utilized. CMP1 which tuned the pore environment with amine functionalities was employed to explore its potential in CO₂ sorption capacities, representing a modest CO₂ uptake of 1.18 mmol g⁻¹ at 298 K and 1 bar.¹²⁴ Later, Han et al. reported a microporous perfluorinated CTF with the BET surface area of 1535 m² g⁻¹ revealing a high CO₂ uptake of 3.41 mmol g⁻¹ at 298 K and 1 bar,¹²⁵ which benefited from the combination of high surface area and electronegative pore environment of this so-called FCTF-1-600 (Fig.10).

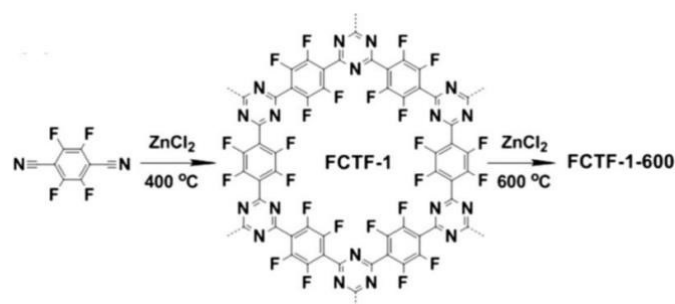


Fig. 10 Synthesis of FCTF with high electronegativity. Adapted with permission.¹²⁵ Copyright 2013, Royal Society of Chemistry.

3.2 Heterogeneous catalysis

The open network of CMPs allows easy access of molecules to transport inner channels of pores, which can be used to increase the enrichment of reactants surrounding catalytic sites, thus improving the catalytic efficiency. Jiang et al. reported the first iron-based porphyrin CMP network named Fe-CMP with a high BET surface area of 1270 m² g⁻¹ and plenty of catalytic metalloporphyrin sites, which was synthesized by the polycondensation of iron(III) tetrakis(4'-bromophenyl)porphyrin and 1,4-phenyldiboric acid via a Suzuki-Miyaura cross-coupling reaction.¹¹² The FeP-CMP showed highly active oxidation for sulfide groups with chemoselectivity, and the conversion was as high as 99% with a large turnover number (TON=97,320) (Fig.11). The bifunctional CMP network, FeP-CMP, bearing a high density of catalytic sites in the skeleton and convenient transportation of reactants with high porosity, accelerates the efficiency of catalysis greatly. Therefore, this strategy of constructing efficient catalysis system provides us a blueprint for the further design of a catalyst beginning from the molecular level.



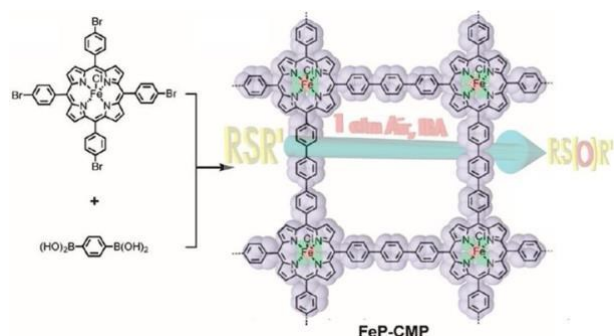


Fig. 11 Synthesis of the nano heterogeneous catalyst with metalloporphyrin built-in skeleton (FeP-CMP). Reproduced with permission.¹¹² Copyright 2010, American Chemical Society.

In addition to the introduction of metal catalytic sites in CMPs to build up a catalysis system, the organic functional group can also serve as the active sites to address the challenging catalytic tasks. Wang et al. demonstrated a bifunctional acidic solid catalyst, PPhen-SO₃H, which was obtained through the attachment of -SO₃H groups to the polyphenylene (PPhen) framework via post-synthetic modification.¹²⁶ PPhen-SO₃H featuring high porosity and unique structure ensures the high accessibility of reactants to the active sites, representing enhanced activity in the hydration of alkynes with the combination of the solvation environments in the structure.

3.3 Photocatalysis

Inspired by the extended π -conjugated networks of CMPs, it is believed that CMPs can be employed to photocatalysis after the nice tuning of their building units or structures. Vilela et al. reported the synthesis for CMPs with the tailoring of specific electronic properties in network, which were then evaluated for the activation of singlet oxygen with the conversion of substrate up to 90 %.⁹⁴ Shortly after their publication, this CMP was medicated by 3-mercaptopropionic acid through thiol-yne click reaction to convert it from hydrophobicity to hydrophilicity.¹²⁷ This modification allows the so-called WCMP to possess higher aqueous compatibility, which promises higher conversion of the substrate in the presence of water in contrast to the original CMPs.

CMPs bearing the feasibility of wide and tunable band gap would be potential candidates for the photocatalytic generation of H₂ from water, and many studies have focused on CMPs in this application.¹²⁸⁻¹³² Copper et al. described a library of pyrene-based CMPs with tunable optical gap via the rational copolymerization of benzene- and pyrene-based monomers, which exhibited great potential advantages for water splitting to generate H₂.¹³³ Recently, Jiang and co-workers reported a series of D- π -A CMPs and evaluated their photocatalytic activities for hydrogen evolution from water.¹³⁴ The so-called PyBS polymers were obtained by the condensation of 1,4-benzenediboronic acid bis(pinacolate) (DBABz) as the π -bridge and varying ratio of 1,3,6,8-tetrabromopyrene (TBrPy) (electron donor) and 3,7-dibromodibenzothiophene-S,S-dioxide (DBrBTDO) (electron acceptor) via a Suzuki-Miyaura cross coupling reaction. Accordingly, the resultant D- π -A CMPs with different chemical composition of electron donor and acceptor showed diverse photocatalytic activities for H₂ generation. Interestingly, the hydrogen evolution rate (HER) for the D- π -A CMPs keeps increasing at first along with the increase

of the content of electron acceptor but starts decreasing when the molar percentage of electron acceptor in the generated CMP skeleton is over 75 %, demonstrating the significance of the rational assembly of electron acceptor and donor in CMP networks to obtain the optimized photocatalytic activity for hydrogen evolution. The resulting PyBS-3 (donor/acceptor: 25/75) combined broad light adsorption region with high hydrophilicity revealed the highest HER among total 4 PyBSs, and a HER of 1.05 mmol h⁻¹ was observed by 10 mg PyBS-3 under UV/Vis light irradiation with Pt as the cocatalyst and ascorbic acid as the sacrificial hole-scavenger.

Besides photocatalytic water splitting to generate H₂, CO₂ capture and photoreduction to useful industrial raw materials is another potential application in bifunctional CMPs.¹³⁵⁻¹³⁷ Liu and co-workers demonstrated the synthesis of several Eosin Y-functionalized CMPs and their photocatalytic activities in the evaluation of CO₂ photoreduction.¹³⁸ PEosinY-1 prepared by the Eosin Y and 1,4-diethynylbenzene in the presence of tetrakis(triphenylphosphine) palladium and cuprous iodide had a BET surface area of 445 m² g⁻¹ with the best performance for the CO₂ photoreduction under visible-light irradiation, affording 92 % selective reduction for CO combining with a production rate up to 33 μ mol g⁻¹ h⁻¹.

Except for the introduction of units with specific electronic properties to the network backbone, the position of these substitutions is also crucial in the design of an effective CMP-based photocatalyst. A family of CMPs with the same photocatalytic sites were introduced by Zhang et al, which were constructed by altering the functionality positions on the core phenyl unit (Fig.12).¹³⁹ With the strategy of fine-tuning substitution, the resulted valence and conduction levels of the CMP networks can be configured optimally according to the requirement for the specific reductive and oxidative potentials needed in the catalytic system, without the molecular change of the electron donor and acceptor moieties in CMP networks. The designed photocatalyst with substitution on the 1,3,5-positions of the phenyl core exhibited exceptional better photocatalytic activity in the oxidative coupling of benzylamines.

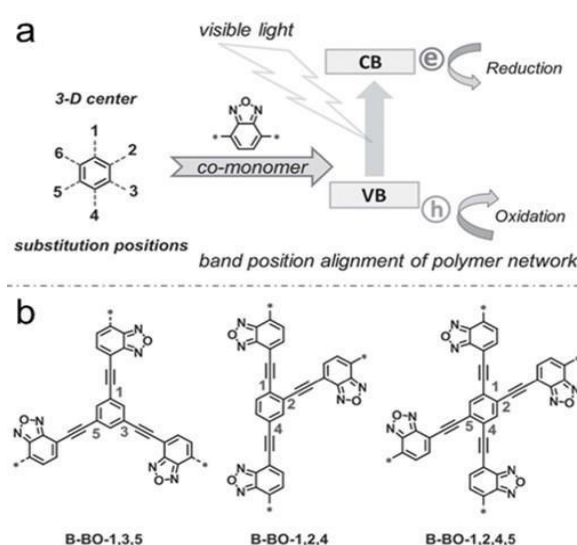


Fig. 12 (a) Geometry design principle of valence and conduction band position modification. (b) Synthesis of CMPs with the substitution



position modification. Reproduced with permission.¹³⁹ Copyright 2015, John Wiley and Sons.

3.4 Light emittance

The restriction for the rotation of phenyl rings in the CMPs network avoids the fluorescent quenching which is very common in the π -conjugated linear polymers. Thus, CMPs can be prepared as luminescent materials with rigid and interlocked building blocks. Cooper et al. first reported that the bandgap of CMPs could be tuned by controlling the molecular structure of building units.¹⁴⁰ Jiang et al. later demonstrated a strategy to construct highly luminescent CMPs through the rational architecture of conjugated building blocks.¹⁴¹ TPE-CMPs were synthesized using tetrakis(4-bromophenyl)ethene (TBTPE) as a single component via Yamamoto coupling reaction under different reaction times from 2 to 72 h (Fig.13). The BET surface areas for TPE-CMPs increase along with the increment of the coupling time, meaning that the TPE-CMPs network can grow larger after a longer reaction time and obtain a higher surface area without the change of pore size distribution. In comparison with the TBTPE monomer, all TPE-CMP networks showed an absorption band with red-shift, suggesting the π -conjugation extension in the interlocked skeletons with the restricted rotation of phenyl units. Furthermore, TPE-CMPs kept strong luminescence in a wide range of common solvents, showing high applicability. The strategy of confining π -conjugated units in the backbone of CMPs not only promotes the π -electronic conjugation but also facilitates exciton migration in CMPs, which indeed extends the development of luminescent materials with bifunctionalities.

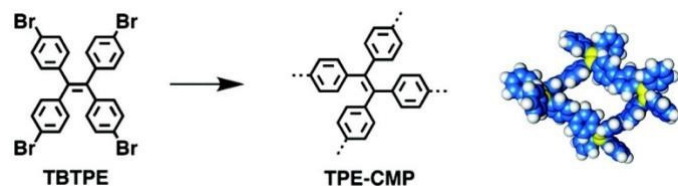


Fig. 13 Synthesis of TPE-CMP with a closed tetragonal skeleton. Reproduced with permission.¹⁴¹ Copyright 2011, American Chemical Society.

3.5 Environmental remediation

The remediation for unclear wastes is a great challenge nowadays. A large number of solid-phase adsorbents have been applied in this field to eliminate unclear contaminations, including metal-organic frameworks,¹⁴² porous organic polymers,^{143,144} and covalent organic frameworks.¹⁴⁵ To enhance the uptake ability, the rational construction of CMPs at the molecular units and pore structure is necessary. Our group reported a bifunctional CMP network owning highly efficient uranium capture via the deliberate introduction of synergistic coordination sites to the skeleton.¹²² The affinity of chelating groups to uranyl is improved greatly with the increasing coordinative binding interactions after bis-amidoxime functionalized groups have been attached to the backbone of CMPs. Additionally, to amplify coordinative binding interactions, we also designed a CMP network with amidoxime and amine groups (CMP-mAO-oNH₂),¹⁴⁶ which exhibited increased uranium adsorption capacity to 174 mg g⁻¹ in contrast to that of amidoxime functionalized CMP network (CMP-mAO) without amine groups (105 mg g⁻¹). From these results, it proves that the synergistic coordination to uranyl with the assist of

electron-donating amino functionalities locating on the *ortho*-position to the amidoxime groups can greatly improve the performance of amidoxime-based adsorbents for uranium uptake.

The long-lived radioactive iodine (¹²⁹I or ¹³¹I) is a persistent problem which can be generated from the fume emission of nuclear power plants with grave public health consequences. Thus, the development of adsorbents with fast and efficient capture of iodine and ready recycle ability is urgent. Faul et al. introduced a family of hexaphenylbenzene-based CMPs with the construction of a hexakis(4-bromophenyl)benzene (HBB) core and various aryl diamine linkers (HCMPs).¹⁴⁷ These CMPs with moderate surface areas and uniform pore shapes ensure the accessibility of iodine molecule (Fig.14). HCMP-3 was synthesized with HBB and *o*-tolidine under a N₂ atmosphere, exhibiting the highest iodine capture up to 316 wt % (3.16 g g⁻¹) among these HCMPs, which benefited from the combination of its microporosity with abundant amine functionality in pore surface providing enough π -electrons. Thus, this synergistic effect endows HCMP-3 with well-defined host-guest interactions, improving the iodine capture with control.

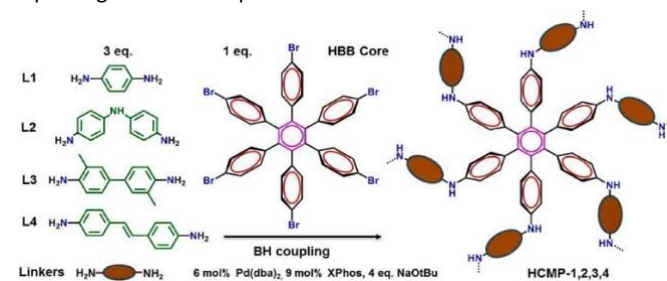


Fig. 14 Synthesis of hexaphenylbenzene-based CMPs. Adapted with permission.¹⁴⁷ Copyright 2016, American Chemical Society.

3.6 Chemical sensing

Jiang et al. synthesized a highly luminescent CMP with the polycondensation of 3,8,13-tribromo 5,10,15-triethyltriindole (TCB) monomer that could be used to detect arenes vapors (Fig.15).¹⁴⁸ TCB-CMP owning large pore surface contacting with arenes and photoluminescence properties originated from its π -conjugated skeleton exhibited fast response times and high sensitivity to arenes. Interestingly, TCB-CMP represents superior fluorescence enhancement when contacting with electron-rich arene vapors, while drastic fluorescence quenching happens when detecting electron-deficient arene vapors.

Dichtel et al. reported a CMP that had fluorescence quenching ability when exposing to 2,4,6-trinitrotoluene (TNT) vapor.¹⁴⁹ The resultant CCP 3 containing 4-dialkoxybenzene substitution was prepared in DMF via a Sonogashira-Hagihara cross-coupling reaction and activated by freeze-drying, which had the highest electronic complementarity to TNT vapor with plenty of π -electron-rich units containing in the skeleton. The success of the combination of high porosity and electron-rich system in CCP 3 suggests that CMP possesses promising application in detecting low-volatility explosives, such as TNT, with the elaborative design of CMP architecture.



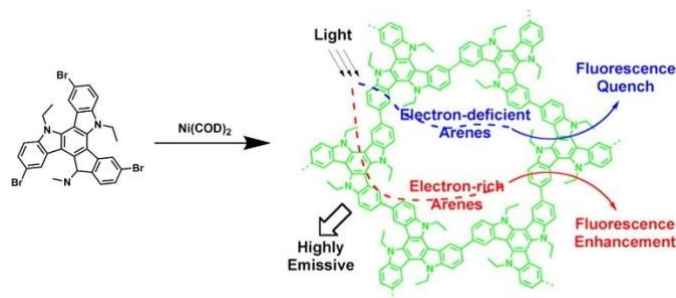


Fig. 15 Synthesis of carbazole-based CMP (TCB-CMP) and schematic of its sensing mechanism. Reproduced with permission.¹⁴⁸ Copyright 2012, American Chemical Society.

3.7 Energy storage

CMPs featuring extended π -conjugated skeletons with permanent micropores are a collection of high-profile porous organic electrode materials in the field of energy storage. A supercapacitor is a type of high-capacity capacitor with a considerably higher capacitance value, storing more than 10 times the charge compared to common capacitors. They are used widely in the area which requires a rapid response for charge/discharge cycles with long-term persistence. In this regard, the high surface areas of CMPs combined with dense active sites allow the fast transportation of charge from the electrolyte to be stored on the edge of the electronic surface, which makes CMPs a candidate for the next-generation supercapacitor. What is more, the ready synthesis of building blocks and easy modification of skeleton ensure high tunability of the chemical and physical properties of CMPs, leading to the sophisticated introduction of redox-active sites to the network with interesting and advantageous properties. In addition, the design principle of batteries is similar to that of supercapacitors. The low conductivity of CMPs, however, is of great challenge which limits their real-life implementation in the field of energy storage, and many efforts have been put forward to address this issue in the past few years.

The first report of aza-fused CMPs for supercapacitive energy storage was described by the Jiang group.¹⁰⁶ They designed a type of CMPs with N-rich property which was linked together by the phenazine ring fusion under high temperature. Interestingly, the resultant CMP networks are conductive, and the microporosity of CMPs results in more surface for electric double-layer capacitance (EDLC) by increasing electrolyte diffusion. Moreover, the aza units in the skeleton enhance the dipolar interactions with the cations of electrolyte, thereby improving proton accumulation on the electronic surface. With the synergistic effect of porosity and the introduction of redox-active sites, the aza-fused CMPs demonstrate distinctive performance for supercapacitive energy storage. The highest capacitance tested under galvanostatic charge-discharge cycling experiments of 0.1 A g^{-1} was reported as 946 F g^{-1} for the Aza-CMP which was synthesized at 450°C with the BET surface area of $1086 \text{ m}^2 \text{ g}^{-1}$. Cooper et al. recently demonstrated a 2D porous carbon material containing sp^2 -hybridized carbons which were synthesized by the condensation of a single monomer, 3-(dibromomethylene)penta-1,4-diyne, using a Sonogashira-Hagihara cross-coupling reaction, while they were supposed to obtain graphyne-type material initially.¹⁵⁰ The yield 2D-PCM with the unique

π -conjugation and hierarchical pore structure was evaluated as an electrode in supercapacitors, showing outstanding electrochemical performance with a capacitance of 378 F g^{-1} at a current density of 0.1 A g^{-1} from galvanostatic charge-discharge cycling experiments.

The first example of a CMP as a cathode in a coin cell was introduced by Jiang and co-workers.¹⁵¹ A N-rich CMP network, by condensing 1,4-diethynylbenzene and 2,3,8,9,14,15-hexaiododiquinoxalino[2,3-a:2',3'-c]phenazine (HIQP), was newly synthesized to qualify the prerequisite as a cathode in Li-ion battery, that is, combining plenty of redox-active sites in the skeleton to store energy with high surface area to maximize charge transportation aiding in easy accessibility to lithium ions. The exploration for the obtained HATN-CM in the application of rechargeable lithium batteries was carried out as a cathode in a coin cell at a current density of 100 mA g^{-1} . HATN-CM exhibited an initial capacity of 147 mA h g^{-1} from the discharge curve when the working potential of HATN-CMP changed from the range 1.5 to 4.0 V versus Li/Li^+ , achieving 71% capability of theoretical capacity, which was higher than that of monomeric HATN equipped as a cathode (56 %). The results obtained from the charge-discharge tests reveals that the CMP skeleton with high porosity enhances the accessibility of redox-active sites for dipolar interactions with the cations, thus improving the performance of energy storage.

Wang et al. demonstrated the first example of crystalline CTF used in Li-S batteries.¹⁵² They prepared the material by the condensation of 1,4-dicyanobenzene in the presence of molten ZnCl_2 at 400°C , then loading the sulfur into the backbone of CTF-1 through a conventional melting-diffusion method to form the composite material with 34 % sulfur loaded according to the weight (Fig.16a). The performance of galvanostatic measurements for CTF-1/S@155C was tested at a current rate of 0.1 C, revealing a high discharge capacity of 1197 mA h g^{-1} at the 2nd cycle with relatively good recyclability. The capacity was decreased to 762 mA h g^{-1} after 50 cycles test with a lower Coulombic efficiency of 97%. The strategy of designing a sulfur cathode by attaching sulfur to the skeleton using CTF as a host evokes further discovery of constructing suitable CTFs which can serve as a qualified cathode material in Li-S battery. Coskun and co-workers reported a sulfur-mediated CTF-1 which was synthesized by the cyclotrimerization of 1,4-dicyanobenzene in the presence of elemental sulfur at 400°C *in situ*.¹⁵³ Sulfur polymerization/insertion happened simultaneously with the CTF framework formation, resulting in a uniform distribution of sulfur with a high loading of 62 wt % (Fig.16b). The original capacity of S-CTF-1 was determined from the potential range 1.7 to 2.7 V versus Li/Li^+ at 0.05 C, as high as 670 mA h g^{-1} . The cooperation of the well-confined sulfur species within the pore porosity and extended π -conjugated skeletons ensures excellent charge conductivity. However, the increment of sulfur content in S-CTF-1 is still inhibited by the crosslinking chemistry of sulfur, which is addressed by Coskun¹⁵⁴ and Wang et al.¹⁵⁵ independently through the simultaneous construction of fluorinated CTF and sulfur-mediated trimerization of tetrafluorophthalonitrile soon later (Fig.16c and d). In this formation, the highly electronegative fluorine atoms in skeletons strengthen the anchoring effect for polysulfides, thereby accelerating the polysulfide conversion and increasing the sulfur content.



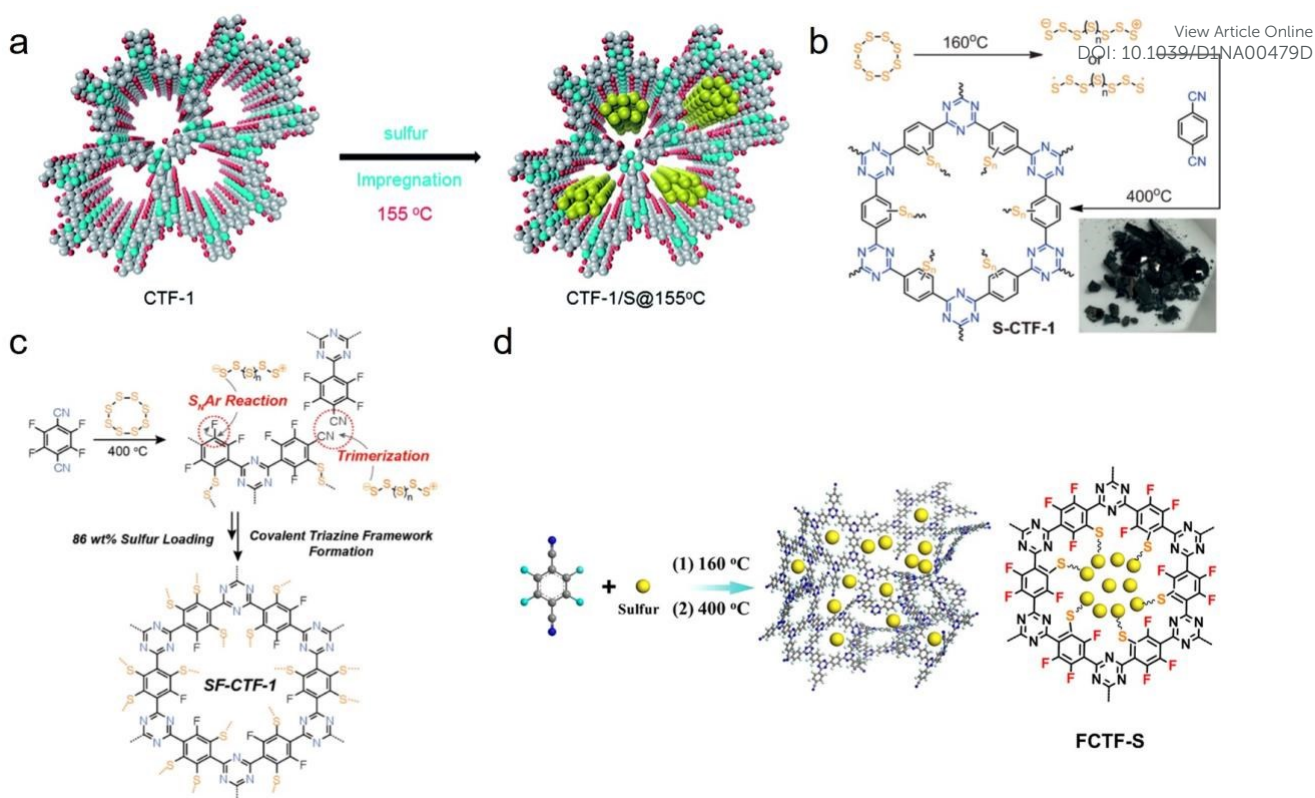


Fig. 16 (a) Synthesis of sulfur-containing CTF-1 by impregnation of molten sulfur. Reproduced with permission.¹⁵² Copyright 2014, Royal Society of Chemistry. (b) Synthesis of S-CTF-1 from elemental sulfur *in situ* and (c) synthesis of SF-CTF-1 involving elemental sulfur-mediated nitrile trimerization along with the simultaneous covalent attachment of elemental sulfur via S_NAr chemistry. Reproduced with permission.^{153,154} Copyright 2016 and 2017, John Wiley and Sons. (d) Synthesis of the FCTF-S composite by one-step sulfur-assisted cyclotrimerization of aromatic nitriles. Reproduced with permission.¹⁵⁵ Copyright 2017, American Chemical Society.

4. Outlooks and Conclusions

CMPs as a member of the family of porous organic polymers bear unique π -conjugated skeletons with permanent micropores which ensure them to be a type of high-profile porous materials, making a difference to many fields of science and technology. In this review, we describe a small portion of the progress in the study of rational design and synthesis for bifunctional CMPs with their advanced applications. The demand for the discovery of real-life implementation of CMPs motivates researchers to optimize the design and functionalization with improved accessibility, which profoundly accelerates the flourish of the field of porous organic polymers. Based on the knowledge of constructing functionality in porous material in the past few years, researchers have developed various methods to functionalize CMPs of interest, including *de novo* synthesis of monomers and post-synthetic modification of CMP networks, which expand the CMP family with unique, sophisticated, and well-designed applications.

As a platform for designing bifunctional porous organic polymers, CMPs enable the introduction of synergistic systems in the skeleton via convenient methods and scalable synthesis. This strategy has proven as a useful toolbox for tailoring the functionality of CMP networks, especially in the fields such as the enhancement of light-

harvesting, introduction of catalytic centers, and development of electronic redox-active sites.

A small fraction of other bifunctional porous organic polymers has also been covered regarding the design and synthesis of synergistic systems in the skeleton, such as COFs. Additionally, the differences between two functionalizing methods, *de novo* synthesis, and post-synthetic modification, have been discussed with the comparison of grafting degree, synthetic complexity, and functional diversity.

Comparing with crystalline covalent organic frameworks, CMPs as amorphous porous organic polymers could be synthesized via simpler and more diverse methods without the consideration of obtaining crystalline structures. However, the surface area of the amorphous CMP would be lower than its COF equivalent and the property of conjugation would also be affected if amorphous, thus influencing the practical performance of CMPs. It is believed that the low crystalline order of CMPs would limit their applications, especially after the successful introduction of conjugated COFs which combine the π -conjugation with crystalline structure in the single skeleton. Such conjugated COFs usually have better a BET surface area and length of conjugation, revealing greater potential than its analogous CMPs. Cooper et al reported their research about crystalline and amorphous CMPs with the same chemical



composition for comparison.¹⁵⁶ Unsurprisingly, the conjugated COF demonstrated a better photocatalytic HER performance compared with that of its analogous disordered CMPs. But most of crystalline COFs are not stable after being treated in a harsh environment; and their performance would decrease along with the loss of crystallinity, while CMPs with rigid structures and disordered networks would have better recyclability and consistency in real-life implementation. To solve this problem, some strategies have been employed recently to increase the stability of COFs and to improve their recyclability in rigorous working conditions.^{157–160} So what is the selling point for CMPs in comparison with COF actually?

Given the discussion of applications of bifunctional CMPs above, the unique selling point would be their extended conjugation in the skeleton and various adaption for conjugation enhancement. Thus, those applications favouring these properties would take advantages of CMPs and benefit from their unique conjugated structures. Such as photocatalysis, batteries and energy storage. A lot of CMPs have been applied to study photoredox catalysis, including photocatalytic oxygen activation, photocatalytic water splitting, and CO₂ photoreduction. Although the development of CMPs in this area have been proceeding for several years, it is still worth exploring because of the expanded photoredox catalysis, such as complex organic synthesis. Traditionally, most photoredox catalysts would contain transition metals but CMPs offer the opportunity to reduce the use of expensive metals and improve the operational reliability and recyclability. Additionally, the band gap of CMPs could be tuned precisely and easily via many methods to fit the requirements of specific photoredox catalysis, making CMP more versatile in multiple applications. Another research area worth exploring for CMPs is batteries and energy storage, the bulk conductivity of most of CMPs, however, limits their capabilities in such area. Therefore, developing CMPs with better conductivity rather than mixing with other conductive materials in use is still a long way to go. We believe CMPs would play a significant role in those challenging tasks after addressing the problems above.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

The authors acknowledge the U.S. National Science Foundation (CBET-1706025) and the Robert A. Welch Foundation (B-0027) for financial support of this work.

Notes and references

- 1 R. M. Barrer, *Zeolites*, 1981, **1**, 130–140.
- 2 R. Fricke, H. Kosslick, G. Lischke and M. Richter, *Chem. Rev.*, 2000, **100**, 2303–2406.
- 3 Y. Wan and D. Zhao, *Chem. Rev.*, 2007, **107**, 2821–2860.
- 4 Z. A. AlOthman, *Materials*, 2012, **5**, 2874–2902.
- 5 H. Furukawa, K. E. Cordova, M. O'Keeffe and O. M. Yaghi, *Science*, 2013, **341**, 1230444.
- 6 H.-C. Zhou and S. Kitagawa, *Chem. Soc. Rev.*, 2014, **43**, 5415–5418.
- 7 S. Kitagawa, R. Kitaura and S.-i. Noro, *Angew. Chem., Int. Ed.*, 2004, **43**, 2334–2375. DOI: 10.1039/D1NA00479D
- 8 W. Lu, Z. Wei, Z.-Y. Gu, T.-F. Liu, J. Park, J. Park, J. Tian, M. Zhang, Q. Zhang, T. Gentle III, M. Bosch and H.-C. Zhou, *Chem. Soc. Rev.*, 2014, **43**, 5561–5593.
- 9 J. R. Long and O. M. Yaghi, *Chem. Soc. Rev.*, 2009, **38**, 1213–1214.
- 10 M. O'Keeffe, *Chem. Soc. Rev.*, 2009, **38**, 1215–1217.
- 11 O. K. Farha and J. T. Hupp, *Acc. Chem. Res.*, 2010, **43**, 1166–1175.
- 12 O. M. Yaghi, M. O'Keeffe, N. W. Ockwig, H. K. Chae, M. Eddaoudi and J. Kim, *Nature*, 2003, **423**, 705–714.
- 13 B. Chen, S. Xiang and G. Qian, *Acc. Chem. Res.*, 2010, **43**, 1115–1124.
- 14 A. P. Côté, A. I. Benin, N. W. Ockwig, M. O'Keeffe, A. J. Matzger and O. M. Yaghi, *Science*, 2005, **310**, 1166.
- 15 C. S. Diercks and O. M. Yaghi, *Science*, 2017, **355**, eaal1585.
- 16 X. Feng, X. Ding and D. Jiang, *Chem. Soc. Rev.*, 2012, **41**, 6010–6022.
- 17 S.-Y. Ding and W. Wang, *Chem. Soc. Rev.*, 2013, **42**, 548–568.
- 18 N. Huang, P. Wang and D. L. Jiang, *Nat. Rev. Mater.*, 2016, **1**, 16068.
- 19 P. Kuhn, M. Antonietti and A. Thomas, *Angew. Chem., Int. Ed.*, 2008, **47**, 3450–3453.
- 20 P. Katekomol, J. Roeser, M. Bojdys, J. Weber and A. Thomas, *Chem. Mater.*, 2013, **25**, 1542–1548.
- 21 Z. Yang, H. Chen, S. Wang, W. Guo, T. Wang, X. Suo, D. E. Jiang, X. Zhu, I. Popovs and S. Dai, *J. Am. Chem. Soc.*, 2020, **142**, 6856–6860.
- 22 C. Krishnaraj, H. S. Jena, K. Leus and P. Van Der Voort, *Green Chem.*, 2020, **22**, 1038–1071.
- 23 M. Liu, L. Guo, S. Jin and B. Tan, *J. Mater. Chem. A*, 2019, **7**, 5153–5172.
- 24 S. Das, P. Heasman, T. Ben and S. L. Qiu, *Chem. Rev.*, 2017, **117**, 1515–1563.
- 25 W. Ji, T.-X. Wang, X. Ding, S. Lei and B.-H. Han, *Coord. Chem. Rev.*, 2021, **439**, 213875.
- 26 P. Kaur, J. Hupp and S. T. Nguyen, *ACS Catal.*, 2011, **1**, 819–835.
- 27 Y. Zhang and S. N. Riduan, *Chem. Soc. Rev.*, 2012, **41**, 2083–2094.
- 28 V. A. Davankov and M. P. Tsyurupa, *React. Polym.*, 1990, **13**, 27–42.
- 29 L. X. Tan and B. Tan, *Chem. Soc. Rev.*, 2017, **46**, 3322–3356.
- 30 J. Huang and S. R. Turner, *Polym. Rev.*, 2017, **6**, 1–41.
- 31 N. Fontanals, R. M. Marce, F. Borrull and P. A. G. Cormack, *Polym. Chem.*, 2015, **6**, 7231–7244.
- 32 T. Ben, H. Ren, S. Ma, D. Cao, J. Lan, X. Jing, W. Wang, J. Xu, F. Deng, J. M. Simmons, S. Qiu and G. Zhu, *Angew. Chem., Int. Ed.*, 2009, **48**, 9457–9460.
- 33 Y. Tian and G. Zhu, *Chem. Rev.*, 2020, **120**, 8934–8986.
- 34 Y. Yuan and G. Zhu, *ACS Cent. Sci.*, 2019, **5**, 409–418.
- 35 T. Ben and S. Qiu, *CrystEngComm*, 2013, **15**, 17–26.
- 36 A. I. Cooper, *Adv. Mater.*, 2009, **21**, 1291–1295.
- 37 Y. Xu, S. Jin, H. Xu, A. Nagai and D. Jiang, *Chem. Soc. Rev.*, 2013, **42**, 8012–8031.
- 38 J.-S. M. Lee and A. I. Cooper, *Chem. Rev.*, 2020, **120**, 2171–2214.
- 39 N. Chaoui, M. Trunk, R. Dawson, J. Schmidt and A. Thomas, *Chem. Soc. Rev.*, 2017, **46**, 3302–3321.
- 40 J. X. Jiang, F. B. Su, A. Trewin, C. D. Wood, N. L. Campbell, H. J. Niu, C. Dickinson, A. Y. Ganin, M. J. Rosseinsky, Y. Z. Khimyak and A. I. Cooper, *Angew. Chem., Int. Ed.*, 2007, **46**, 8574–8578.
- 41 G. Cheng, T. Hasell, A. Trewin, D. J. Adams and A. I. Cooper, *Angew. Chem., Int. Ed.*, 2012, **51**, 12727–12731.
- 42 P. Pallavi, S. Bandyopadhyay, J. Louis, A. Deshmukh and A. Patra, *Chem. Commun.*, 2017, **53**, 1257–1260.



- 43 B. Huang, P. Zhao, Y. Dai, S. Deng and A. Hu, *J. Polym. Sci., Part A: Polym. Chem.*, 2016, **54**, 2285–2290.
- 44 R. Chinchilla and C. Nájera, *Chem. Soc. Rev.*, 2011, **40**, 5084–5121.
- 45 A. Suzuki, *Angew. Chem., Int. Ed.*, 2011, **50**, 6723–6737.
- 46 A. Suzuki, *Chem. Commun.*, 2005, 4759–4763.
- 47 T. Yamamoto, A. Morita, Y. Miyazaki, T. Maruyama, H. Wakayama, Z.-h. Zhou, Y. Nakamura and T. Kanbara, *Macromolecules*, 1992, **25**, 1214–1223.
- 48 I. P. Beletskaya and A. V. Cheprakov, *Chem. Rev.*, 2000, **100**, 3009–3066.
- 49 S.-L. You, Q. Cai and M. Zhang, *Chem. Soc. Rev.*, 2009, **38**, 2190–2201.
- 50 T. B. Poulsen and K. A. Jørgensen, *Chem. Rev.*, 2008, **108**, 2903–2915.
- 51 J. K. Stille, E. Mainen, *J. Polym. Sci., Part B: Polym. Lett.*, 1966, **4**, 39–41.
- 52 J. K. Stille, E. L. Mainen, *Macromolecules*, 1968, **1**, 36–42.
- 53 W. Shi, C. Liu and A. Lei, *Chem. Soc. Rev.*, 2011, **40**, 2761–2776.
- 54 E. H. Cordes and W. P. Jencks, *J. Am. Chem. Soc.*, 1962, **84**, 832–837.
- 55 J. L. Segura, M. J. Manchenõa and F. Zamora, *Chem. Soc. Rev.*, 2016, **45**, 5635–5671.
- 56 V. Gevorgyan and Y. Yamamoto, *J. Organomet. Chem.*, 1999, **576**, 232–247.
- 57 S. Kotha, E. Brahmachary and K. Lahiri, *Eur. J. Org. Chem.*, 2005, 4741–4767.
- 58 C. Zhang, X. Yang, Y. Zhao, X. Wang, M. Yu and J.-X. Jiang, *Polymer*, 2015, **61**, 36–41.
- 59 Q. Shi, H. Sun, R. Yang, Z. Q. Zhu, W. Liang, D. Tan, B. Yang, A. Li and W. Deng, *J. Mater. Sci.*, 2015, **50**, 6388–6394.
- 60 P. Lindemann, M. Tsotsalas, S. Shishatskiy, V. Abetz, P. Kroll-Sidenstein, C. Azucena, L. Monnereau, A. Beyer, A. Götzhäuser, V. Mugnaini, H. Gliemann, S. Bräse and C. Wöll, *Chem. Mater.*, 2014, **26**, 7189–7193.
- 61 D. Z. Tan, W. J. Fan, W. N. Xiong, H. X. Sun, A. Li, W. Q. Deng and C. G. Meng, *Eur. Polym. J.*, 2012, **48**, 705–711.
- 62 W. Lu, Z. Wei, D. Yuan, J. Tian, S. Fordham and H.-C. Zhou, *Chem. Mater.*, 2014, **26**, 4589–4597.
- 63 Y. Xie, T. T. Wang, R. X. Yang, N. Y. Huang, K. Zou and W. Q. Deng, *ChemSusChem*, 2014, **7**, 2110–2114.
- 64 Y.-B. Zhou and Z.-P. Zhan, *Chem. – Asian J.*, 2018, **13**, 9–19.
- 65 Y. Z. Liao, Z. H. Cheng, W. W. Zuo, A. Thomas and C. F. J. Faul, *ACS Appl. Mater. Interfaces*, 2017, **9**, 38390–38400.
- 66 S. Tantisriyanurak, H. N. Duguid, L. Peattie and R. Dawson, *ACS Appl. Polym. Mater.*, 2020, **2**, 3908–3915.
- 67 X. Wang, S.-M. Lu, J. Li, Y. Liu and C. Li, *Catal. Sci. Technol.*, 2015, **5**, 2585–2589.
- 68 N. Kang, J. H. Park, K. C. Ko, J. Chun, E. Kim, H.-W. Shin, S. M. Lee, H. J. Kim, T. K. Ahn, J. Y. Lee and S. U. Son, *Angew. Chem., Int. Ed.*, 2013, **52**, 6228–6232.
- 69 Z. J. Wang, S. Ghasimi, K. Landfester and K. A. I. Zhang, *Chem. Commun.*, 2014, **50**, 8177–8180.
- 70 Z. J. Wang, S. Ghasimi, K. Landfester and K. A. I. Zhang, *Chem. Mater.*, 2015, **27**, 1921–1924.
- 71 X. Liu, Y. Zhang, H. Li, A. Sigen, H. Xia and Y. Mu, *RSC Adv.*, 2013, **3**, 21267–21270.
- 72 P. Zhang, K. Wu, J. Guo and C. Wang, *ACS Macro Lett.*, 2014, **3**, 1139–1144.
- 73 B. Bonillo, R. S. Sprick and A. I. Cooper, *Chem. Mater.*, 2016, **28**, 3469–3480.
- 74 A. Sigen, Y. Zhang, Z. Li, H. Xia, M. Xue, X. Liu and Y. Mu, *Chem. Commun.*, 2014, **50**, 8495–8498.
- 75 T. M. Geng, Z. M. Zhu, W. Y. Zhang and Y. Wang, *J. Mater. Chem. A*, 2017, **5**, 7612–7617.
- 76 Y. Liu, Y. Cui, C. Zhang, J. Du, S. Wang, Y. Bai, Z. Liang and X. Song, *Chem.–Eur. J.*, 2018, **24**, 7480–7488.
- 77 M. Xu, T. Wang, P. Gao, L. Zhao, L. Zhou and D. Hua, *J. Mater. Chem. A*, 2019, **7**, 11214–11222. DOI: 10.1039/D1NA00479D
- 78 L. Sun, Z. Liang, J. Yu and R. Xu, *Polym. Chem.*, 2013, **4**, 1932–1938.
- 79 L. B. Sun, Y. C. Zou, Z. Q. Liang, J. H. Yu and R. R. Xu, *Polym. Chem.*, 2014, **5**, 471–478.
- 80 T. M. Geng, H. Zhu, W. Song, F. Zhu and Y. Wang, *J. Mater. Sci.*, 2016, **51**, 4104–4114.
- 81 Z. Li, Y. Zhi, X. Feng, X. Ding, Y. Zou, X. Liu and Y. Mu, *Chem. – Eur. J.*, 2015, **21**, 17355–17362.
- 82 X. Zhuang, F. Zhang, D. Wu, N. Forler, H. Liang, M. Wagner, D. Gehrig, M. R. Hansen, F. Laquai and X. Feng, *Angew. Chem., Int. Ed.*, 2013, **52**, 9668–9672.
- 83 H. Zhang, Y. Zhang, C. Gu and Y. Ma, *Adv. Energy Mater.*, 2015, **5**, 1402175.
- 84 Q. Zhang, S. Ge, X. Wang, H. Sun, Z. Zhu, W. Liang and A. Li, *RSC Adv.*, 2014, **4**, 41649–41653.
- 85 S. Zhang, W. Huang, P. Hu, C. Huang, C. Shang, C. Zhang, R. Yang and G. Cui, *J. Mater. Chem. A*, 2015, **3**, 1896–1901.
- 86 C. Zhang, Y. He, P. Mu, X. Wang, Q. He, Y. Chen, J. Zeng, F. Wang, Y. Xu and J. Jiang, *Adv. Funct. Mater.*, 2018, **28**, 1705432.
- 87 K. Ding, Q. Liu, Y. Bu, K. Meng, W. Wang, D. Yuan and Y. Wang, *J. Alloys Compd.*, 2016, **657**, 626–630.
- 88 N. Miyaoura, K. Yamada and A. Suzuki, *Tetrahedron Lett.*, 1979, **20**, 3437–3440.
- 89 N. Miyaoura and A. Suzuki, *J. Chem. Soc., Chem. Commun.*, 1979, 866–867.
- 90 A. Kirchon, L. Feng, H. F. Drake, E. A. Joseph and H.-C. Zhou, *Chem. Soc. Rev.*, 2018, **47**, 8611–8638.
- 91 Z. Wang and S. M. Cohen, *J. Am. Chem. Soc.*, 2007, **129**, 12368–12369.
- 92 Y. Song, Q. Sun, B. Aguila and S. Ma, *Adv. Sci.*, 2018, **6**, 1801410.
- 93 Y. Yusran, X. Guan, H. Li, Q. Fang and S. Qiu, *Natl. Sci. Rev.*, 2020, **7**, 170–190.
- 94 K. Zhang, D. Kopetzki, P. H. Seeberger, M. Antonietti and F. Vilela, *Angew. Chem., Int. Ed.*, 2013, **52**, 1432–1436.
- 95 J.-X. Jiang, Y. Li, X. Wu, J. Xiao, D. J. Adams and A. I. Cooper, *Macromolecules*, 2013, **46**, 8779–8783.
- 96 C.-A. Wang, Y.-W. Li, X.-L. Cheng, J.-P. Zhang and Y.-F. Han, *RSC Adv.*, 2017, **7**, 408–414.
- 97 T. Zhang and W. Lin, *Chem. Soc. Rev.*, 2014, **43**, 5982–5993.
- 98 M. Bhadra, S. Kandambeth, M. K. Sahoo, M. Addicoat, E. Balaraman and R. Banerjee, *J. Am. Chem. Soc.*, 2019, **141**, 6152–6156.
- 99 W. Li, X. Huang, T. Zeng, Y. A. Liu, W. Hu, H. Yang, Y. B. Zhang and K. Wen, *Angew. Chem., Int. Ed.*, 2021, **60**, 1869–1874.
- 100 Q. Liu, Z. Tang, M. Wu and Z. Zhou, *Polym. Int.*, 2014, **63**, 381–392.
- 101 L. Chen, Y. Honsho, S. Seki and D. Jiang, *J. Am. Chem. Soc.*, 2010, **132**, 6742–6748.
- 102 S. Bhunia, K. Bhunia, B. C. Patra, S. K. Das, D. Pradhan, A. Bhaumik, A. Pradhan and S. Bhattacharya, *ACS Appl. Mater. Interfaces*, 2019, **11**, 1520–1528.
- 103 H.-J. Zhu, M. Lu, Y.-R. Wang, S.-J. Yao, M. Zhang, Y.-H. Kan, J. Liu, Y. Chen, S.-L. Li and Y.-Q. Lan, *Nat. Commun.*, 2020, **11**, 497.
- 104 Y. Xie, T. T. Wang, X. H. Liu, K. Zou and W. Q. Deng, *Nat. Commun.*, 2013, **4**, 1960.
- 105 L.-H. Li, X.-L. Feng, X.-H. Cui, Y.-X. Ma, S.-Y. Ding and W. Wang, *J. Am. Chem. Soc.*, 2017, **139**, 6042–6045.
- 106 Y. Kou, Y. Xu, Z. Guo and D. Jiang, *Angew. Chem., Int. Ed.*, 2011, **50**, 8753–8757.
- 107 A. B. Marco, D. Cortizo-Lacalle, I. Perez-Miqueo, G. Valenti, A. Boni, J. Plas, K. Strutynski, S. De Feyter, F. Paolucci, M. Montes, A. N. Khlobystov, M. Melle-Franco and A. Mateo-Alonso, *Angew. Chem., Int. Ed.*, 2017, **56**, 6946–6951.



- 108 B. F. Hoskins and R. Robson, *J. Am. Chem. Soc.*, 1990, **112**, 1546–1554.
- 109 Y. Y. Cui, C. X. Yang and X. P. Yan, *ACS Appl. Mater. Interfaces*, 2020, **12**, 4954–4961.
- 110 Y. Zhang and S. N. Riduan, *Chem. Soc. Rev.*, 2012, **41**, 2083–2094.
- 111 J. L. Segura, S. Royuela and M. M. Ramos, *Chem. Soc. Rev.*, 2019, **48**, 3903–3945.
- 112 L. Cheng, Y. Yang and D. Jiang, *J. Am. Chem. Soc.*, 2010, **132**, 9138–9143.
- 113 J. X. Jiang, C. Wang, A. Laybourn, T. Hasell, B. Clowes and A. I. Cooper, *Angew. Chem., Int. Ed.*, 2011, **50**, 1072–1075.
- 114 Y. Mohr, M. Alvas-Favaro, R. Rajapaksha, G. Hisler, A. Ranscht, P. Samanta, C. Lorentz, M. Duguet, C. Mellot-Draznieks, E. A. Quadrelli, F. M. Wisser and J. Canivet, *ACS Catal.*, 2021, **11**, 3507–3515.
- 115 A. Nagai, Z. Guo, X. Feng, S. Jin, X. Chen, X. Ding and D. Jiang, *Nat. Commun.*, 2011, **2**, 536.
- 116 H. Xu, J. Gao and D. L. Jiang, *Nat. Chem.*, 2015, **7**, 905–912.
- 117 Q. Sun, B. Aguila, J. Perman, L. D. Earl, C. W. Abney, Y. Cheng, H. Wei, N. Nguyen, L. Wojtas and S. Ma, *J. Am. Chem. Soc.*, 2017, **139**, 2786–2793.
- 118 B. Kiskan and J. Weber, *ACS Macro Lett.*, 2012, **1**, 37–40.
- 119 X. Wang, X. Zhao, W. Dong, X. Zhang, Y. Xiang, Q. Huang and H. Chen, *J. Mater. Chem. A*, 2019, **7**, 16277–16284.
- 120 T. Ratvijitvech, R. Dawson, A. Laybourn, Y. Z. Khimyak, D. J. Adams and A. I. Cooper, *Polymer*, 2014, **55**, 321–325.
- 121 D. Cui, C. Yao and Y. Xu, *Chem. Commun.*, 2017, **53**, 11422–11425.
- 122 L. Zhang, N. Pu, B. Yu, G. Ye, J. Chen, S. Xu and S. Ma, *ACS Appl. Mater. Interfaces*, 2020, **12**, 3688–3696.
- 123 Y. Liu, S. Wang, X. Meng, Y. Ye, X. Song, Z. Liang and Y. Zhao, *Angew. Chem., Int. Ed.*, 2020, **59**, 19487–19493.
- 124 R. Dawson, D. J. Adams and A. I. Cooper, *Chem. Sci.*, 2011, **2**, 1173–1177.
- 125 Y. Zhao, K. X. Yao, B. Teng, T. Zhang and Y. Han, *Energy Environ. Sci.*, 2013, **6**, 3684–3692.
- 126 Y. Liu, B. Wang, L. Kang, A. Stamatopoulos, H. Gu and F. R. Wang, *Chem. Mater.*, 2020, **32**, 4375–4382.
- 127 H. Urakami, K. Zhang and F. Vilela, *Chem. Commun.*, 2013, **49**, 2353–2355.
- 128 R. S. Sprick, B. Bonillo, M. Sachs, R. Clowes, J. R. Durrant, D. J. Adams and A. I. Cooper, *Chem. Commun.*, 2016, **52**, 10008–10011.
- 129 L. Wang, Y. Wan, Y. Ding, S. Wu, Y. Zhang, X. Zhang, G. Zhang, Y. Xiong, X. Wu, J. Yang and H. Xu, *Adv. Mater.*, 2017, **29**, 1702428.
- 130 Z. Wang, X. Yang, T. Yang, Y. Zhao, F. Wang, Y. Chen, J. H. Zeng, C. Yan, F. Huang and J.-X. Jiang, *ACS Catal.*, 2018, **8**, 8590–8596.
- 131 J. Yu, X. Sun, X. Xu, C. Zhang and X. He, *Appl. Catal., B*, 2019, **257**, 117935.
- 132 C. Yang, B. C. Ma, L. Zhang, S. Lin, S. Ghasimi, K. Landfester, K. A. I. Zhang and X. Wang, *Angew. Chem., Int. Ed.*, 2016, **55**, 9202–9206.
- 133 R. Sprick, J. Jiang, B. Bonillo, S. Ren, T. Ratvijitvech, P. Guiglion, M. A. Zwijnenburg, D. J. Adams and A. I. Cooper, *J. Am. Chem. Soc.*, 2015, **137**, 3265–3270.
- 134 C. Shu, C. Han, X. Yang, C. Zhang, Y. Chen, S. Ren, F. Wang, F. Huang and J.-X. Jiang, *Adv. Mater.*, 2021, **33**, 2008498.
- 135 F. M. Wisser, P. Berruyer, L. Cardenas, Y. Mohr, E. A. Quadrelli, A. Lesage, D. Farrusseng and J. Canivet, *ACS Catal.*, 2018, **8**, 1653–1661.
- 136 C. Yang, W. Huang, L. C. da Silva, K. A. I. Zhang and X. Wang, *Chem. – Eur. J.*, 2018, **24**, 17454–17458.
- 137 C. Dai, L. Zhong, X. Gong, L. Zeng, C. Xue, S. Li and B. Liu, *Green Chem.*, 2019, **21**, 6606–6610.
- 138 X. Yu, Z. Yang, B. Qiu, S. Guo, P. Yang, B. Yu, H. Zhang, Y. Zhao, X. Yang, B. Han and Z. Liu, *Angew. Chem., Int. Ed.*, 2019, **58**, 632–636.
- 139 Z. J. Wang, S. Ghasimi, K. Landfester and K. A. I. Zhang, *Adv. Mater.*, 2015, **27**, 6265–6270.
- 140 J. X. Jiang, A. Trewin, D. J. Adams and A. I. Cooper, *Chem. Sci.*, 2011, **2**, 1777–1781.
- 141 Y. H. Xu, L. Chen, Z. Q. Guo, A. Nagai and D. Jiang, *J. Am. Chem. Soc.*, 2011, **133**, 17622–17625.
- 142 H. Zhang, W. Liu, A. Li, D. Zhang, X. Li, F. Zhai, L. Chen, L. Chen, Y. Wang and S. Wang, *Angew. Chem., Int. Ed.*, 2019, **58**, 16110–16114.
- 143 Q. Sun, L. Zhu, B. Aguila, P. K. Thallapally, C. Xu, J. Chen, S. Wang, D. Rogers and S. Ma, *Nat. Commun.*, 2019, **10**, 1646.
- 144 Q. Sun, B. Aguila, J. Perman, A. S. Ivanov, V. S. Bryantsev, L. D. Earl, C. W. Abney, L. Wojtas and S. Ma, *Nat. Commun.*, 2018, **9**, 1644.
- 145 Q. Sun, B. Aguila, L. D. Earl, C. W. Abney, L. Wojtas, P. K. Thallapally and S. Ma, *Adv. Mater.*, 2018, **30**, 1705479.
- 146 B. Yu, L. Zhang, G. Ye, Q. Liu, J. Li, X. Wang, J. Chen, S. Xu and S. Ma, *Nano Res.*, 2021, **3**, 788–796.
- 147 Y. Liao, J. Weber, B. M. Mills, Z. Ren and C. F. J. Faul, *Macromolecules*, 2016, **49**, 6322–6333.
- 148 X. Liu, Y. Xu and D. Jiang, *J. Am. Chem. Soc.*, 2012, **134**, 8738–8741.
- 149 J. L. Novotney and W. R. Dichtel, *ACS Macro Lett.*, 2013, **2**, 423–426.
- 150 Y. Xu, R. S. Sprick, N. J. Brownbill, F. Blanc, Q. Li, J. W. Ward, S. Ren and A. I. Cooper, *J. Mater. Chem. A*, 2021, **9**, 3303–3308.
- 151 F. Xu, X. Chen, Z. Tang, D. Wu, R. Fu and D. Jiang, *Chem. Commun.*, 2014, **50**, 4788–4790.
- 152 H. Liao, H. Ding, B. J. Li, X. Ai and C. Wang, *J. Mater. Chem. A*, 2014, **2**, 8854–8858.
- 153 S. N. Talapaneni, T. H. Hwang, S. H. Je, O. Buyukcikir, J. W. Choi and A. Coskun, *Angew. Chem., Int. Ed.*, 2016, **55**, 3106–3111.
- 154 S. H. Je, H. J. Kim, J. Kim, J. W. Choi and A. Coskun, *Adv. Funct. Mater.*, 2017, **27**, 1703947.
- 155 F. Xu, S. Yang, G. Jiang, Q. Ye, B. Wei and H. Wang, *ACS Appl. Mater. Interfaces*, 2017, **9**, 37731–37738.
- 156 X. Wang, L. Chen, S. Y. Chong, M. A. Little, Y. Wu, W.-H. Zhu, R. Clowes, Y. Yan, M. A. Zwijnenburg, R. S. Sprick and A. I. Cooper, *Nat. Chem.*, 2018, **10**, 1180–1189.
- 157 S. Kandambeth, V. Venkatesh, D. B. Shinde, S. Kumari, A. Halder, S. Verma and R. Banerjee, *Nat. Commun.*, 2015, **6**, 6786.
- 158 P.-F. Wei, M.-Z. Qi, Z.-P. Wang, S.-Y. Ding, W. Yu, Q. Liu, L.-K. Wang, H.-Z. Wang, W.-K. An and W. Wang, *J. Am. Chem. Soc.*, 2018, **140**, 4623–4631.
- 159 X. Li, C. Zhang, S. Cai, X. Lei, V. Altoe, F. Hong, J. J. Urban, J. Ciston, E. M. Chan and Y. Liu, *Nat. Commun.*, 2018, **9**, 2998.
- 160 J. Liu, T. Yang, Z.-P. Wang, P.-L. Wang, J. Feng, S.-Y. Ding and W. Wang, *J. Am. Chem. Soc.*, 2020, **142**, 20956–20961.

