

State of the Art and Prospects for Halide Perovskite Nanocrystals

Amrita Dey, Junzhi Ye, Apurba De, Elke Debroye, Seung Kyun Ha, Eva Bladt, Anuraj S. Kshirsagar, Ziyu Wang, Jun Yin, Yue Wang, Li Na Quan, Fei Yan, Mengyu Gao, Xiaoming Li, Javad Shamsi, Tushar Debnath, Muhan Cao, Manuel A. Scheel, Sudhir Kumar, Julian A. Steele, Marina Gerhard, Lata Chouhan, Ke Xu, Xian-gang Wu, Yanxiu Li, Yangning Zhang, Anirban Dutta, Chuang Han, Ilka Vincon, Andrey L. Rogach, Angshuman Nag, Anunay Samanta, Brian A. Korgel, Chih-Jen Shih, Daniel R. Gamelin, Dong Hee Son, Haibo Zeng, Haizheng Zhong, Handong Sun, Hilmi Volkan Demir, Ivan G. Scheblykin, Iván Mora-Seró, Jacek K. Stolarczyk, Jin Z. Zhang, Jochen Feldmann, Johan Hofkens, Joseph M. Luther, Julia Pérez-Prieto, Liang Li, Liberato Manna, Maryna I. Bodnarchuk, Maksym V. Kovalenko, Maarten B. J. Roeffaers, Narayan Pradhan, Omar F. Mohammed, Osman M. Bakr, Peidong Yang, Peter Müller-Buschbaum, Prashant V. Kamat, Qiaoliang Bao, Qiao Zhang, Roman Krahne, Raquel E. Galian, Samuel D. Stranks, Sara Bals, Vasudevanpillai Biju, William A. Tisdale, Yong Yan, Robert L. Z. Hoye,* and Lakshminarayana Polavarapu*



Cite This: *ACS Nano* 2021, 15, 10775–10981



Read Online

ACCESS |

Metrics & More

Article Recommendations

Supporting Information

ABSTRACT: Metal-halide perovskites have rapidly emerged as one of the most promising materials of the 21st century, with many exciting properties and great potential for a broad range of applications, from photovoltaics to optoelectronics and photocatalysis. The ease with which metal-halide perovskites can be synthesized in the form of brightly luminescent colloidal nanocrystals, as well as their tunable and intriguing optical and electronic properties, has attracted researchers from different disciplines of science and technology. In the last few years, there has been a significant progress in the shape-controlled synthesis of perovskite nanocrystals and understanding of their properties and applications. In this comprehensive review, researchers having expertise in different fields (chemistry, physics, and device engineering) of metal-halide perovskite nanocrystals have joined together to provide a state of the art overview and future prospects of metal-halide perovskite nanocrystal research.

KEYWORDS: metal-halide perovskite nanocrystals, perovskite nanoplatelets, perovskite nanocubes, perovskite nanowires, lead-free perovskite nanocrystals, light-emitting devices, photovoltaics, lasers, photocatalysts, photodetectors



The earliest research work on metal-halide perovskites (MHPs) was conducted in the late 1800s by Wells,¹ while the detailed structural characterization was carried out by Weber in the 1900s.^{2–4} Their potential applications in electronic and optical devices attracted attention in the late 1990s and the early 2000s, long before captivating the broad scientific community.^{5,6} In 2009, Kojima *et al.*⁷ demonstrated the use of lead-halide perovskites (LHPs) as visible-light sensitizers in solar cells, but it took another 3 years to fully grasp their potential for highly efficient photovoltaics.^{8,9} Since then, the number of researchers

working on MHPs has been increasing significantly over the years, accompanied by a substantial increase in research output in this area. The high efficiency of LHP photovoltaic cells is attributed to long charge carrier diffusion lengths along with

Received: December 16, 2020

Accepted: May 4, 2021

Published: June 17, 2021



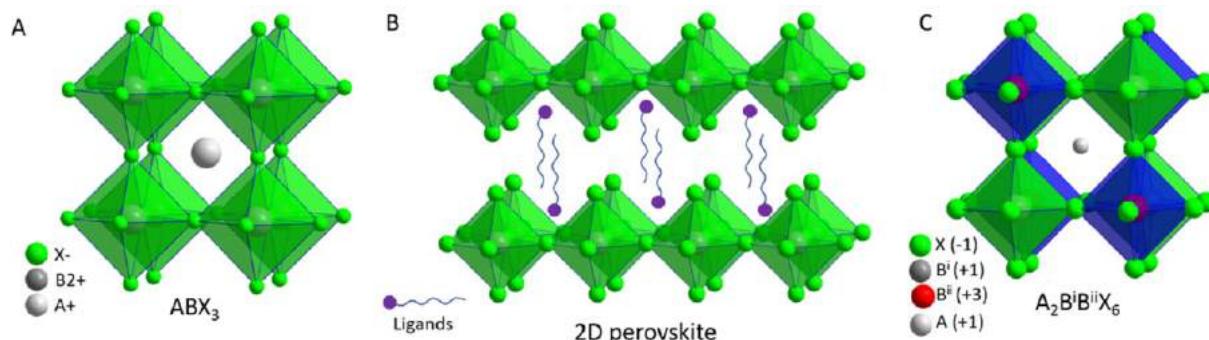


Figure 1. Illustrations of cubic crystal structure of (A) 3D perovskites, (B) 2D-layered perovskites, and (C) 3D double perovskite.

low Urbach energies, high photoluminescence quantum yields, and high absorption coefficients.^{10,11} These significant features are of interest not only for the device communities but also for the chemistry, physics, and materials research communities. Over the last decade, numerous advances have been made toward the fundamental understanding as well as potential applications of MHPs. The certified power conversion efficiency (PCE) of single-junction perovskite-based solar cells has surpassed 25% in a short span of time, demonstrating an order of magnitude higher rate of improvement compared to other photovoltaic technologies.¹² MHPs have recently emerged at the forefront of materials research not only because of their impressive photovoltaic performance but also due to their attractive optical and electronic properties.^{10,11,13–30} Over the years, they have already shown great promise in a wide range of technological applications encompassing photovoltaics (PVs), light-emitting diodes (LEDs), lasers, transistors, photodetectors, and photocatalysts.^{27,31–45} The optical and electronic properties of MHPs were shown to be strongly dependent on their dimensionality (both structural and morphological).^{6,14,16,18,22,30,46–50}

Three-dimensional (3D) MHPs refer to a class of crystalline compounds adopting the generic chemical formula ABX_3 , where the cation “B” has six nearest-neighbor anions “X”, while the cation “A” sits in a cavity formed by eight corner-sharing BX_6 octahedra.^{10,51,52} MHPs are generally classified into either organic–inorganic hybrid (OIH) or inorganic perovskites depending on whether the A-site cation is organic or inorganic. OIH perovskites generally have methylammonium (MA) or formamidinium (FA) as the monovalent A-site cation, lead, tin, or germanium as the divalent B cation and chlorine, bromine, iodine, or their combinations as the halide ion (X). On the other hand, inorganic perovskites have cesium (Cs) or rubidium (Rb) as the A cation. The ideal structure of the perovskite, which is illustrated in Figure 1A, is based on a cubic lattice. However, the deviation from the ideal perovskite structure in ABX_3 materials can be predicted through the Goldschmidt tolerance factor t ($t = (r_A + r_X)/[\sqrt{2}(r_B + r_X)]$), where r_A , r_B , and r_X are the ionic radii of the corresponding ions, and t is defined as the ratio of the distance A–X to the distance B–X. Unlike classical semiconductors (such as Ge, Si, GaAs, CdS, CdSe, InP), high-quality MHPs can be prepared by simply mixing the corresponding precursor solutions at room temperature (RT) under ambient conditions due to their inherent ionic character.^{29,53,54} The optical properties of MHPs are easily tunable across the visible spectrum of light by simply varying the halide composition.^{30,55–57} While the bulk properties of MHP are significant, decreasing the size of

the crystals to the nanoscale reveals their size-dependent optical and electronic properties. For instance, nanosized crystals (nanocrystals, NCs) of MHP exhibit quantum-confinement effects that can be exploited to tune the optical properties,^{14,16,19,22} much like in other semiconductors.^{58,59} The structural dimensionality of MHPs is easily tunable from 3D to 2D using long-chain alkylammonium cations in their synthesis (Figure 1B). The emission wavelength and exciton binding energies of these layered perovskites are controllable by the number of octahedral layers between the long-chain organic layers ($n = 1$ to ∞).^{49,60,61} The tunable emission wavelength, narrow emission, and low nonradiative losses of MHPs make them potential candidates for LEDs. In addition, the long charge carrier diffusion lengths in MHPs facilitate efficient recombination of electrically injected charge carriers. Bulk perovskites suffer from low photoluminescence quantum yields (PLQYs) due to inherent defects, particularly those present at grain boundaries, surfaces, and interfaces.^{15,62,63} On the other hand, MHP NCs appeared as extremely efficient light emitters with near-unity PLQY. The early reports on colloidal halide perovskites emerged in 2012–2014.^{64–66} Despite limited control over the size, shape, and colloidal stability, those early papers showed that such fine perovskite particles exhibit much enhanced emissivity, as evidenced by a PLQY of ~20% for $MAPbBr_3$ colloids.⁶⁶ In late 2014, Gonzalez-Carrero *et al.*²⁵ reported an improved synthesis of highly luminescent $MAPbBr_3$ colloids in toluene. Although the particles were found to be polydisperse and irregularly shaped, as seen from the transmission electron microscopy (TEM) images, they exhibited an impressive PLQY of 80% and stood in drastic contrast to classical colloidal quantum dots (QDs), such as those made of CdSe and InP, which must be epitaxially overcoated with wider-band-gap inorganic shells, such as CdS or ZnS, for imparting high PLQY values.⁶⁷ The most relevant colloidal synthesis of well-defined colloidal LHP NCs, which enabled exquisite control over the size and size distribution and thermodynamic stability of colloids, was the one by Protesescu *et al.* in January 2015 using the hot-injection (HI) method, which delivered monodisperse $CsPbX_3$ NCs.¹⁴ These $CsPbX_3$ NCs not only exhibited PLQY values up to 100% but also showed quantum-size effects similar to classical QDs. In March 2015, Zhang *et al.* introduced the ligand-assisted reprecipitation (LARP) approach for the room-temperature synthesis of $MAPbX_3$ NCs with color-tunable emission and PLQY up 70%.²⁹ In the same year, Tyagi *et al.*¹⁹ and Sichert *et al.*¹⁶ simultaneously reported the preparation of $MAPbBr_3$ perovskite nanoplatelets (NPLs). The precise control of the number of monolayers in the platelets, down to monolayer,

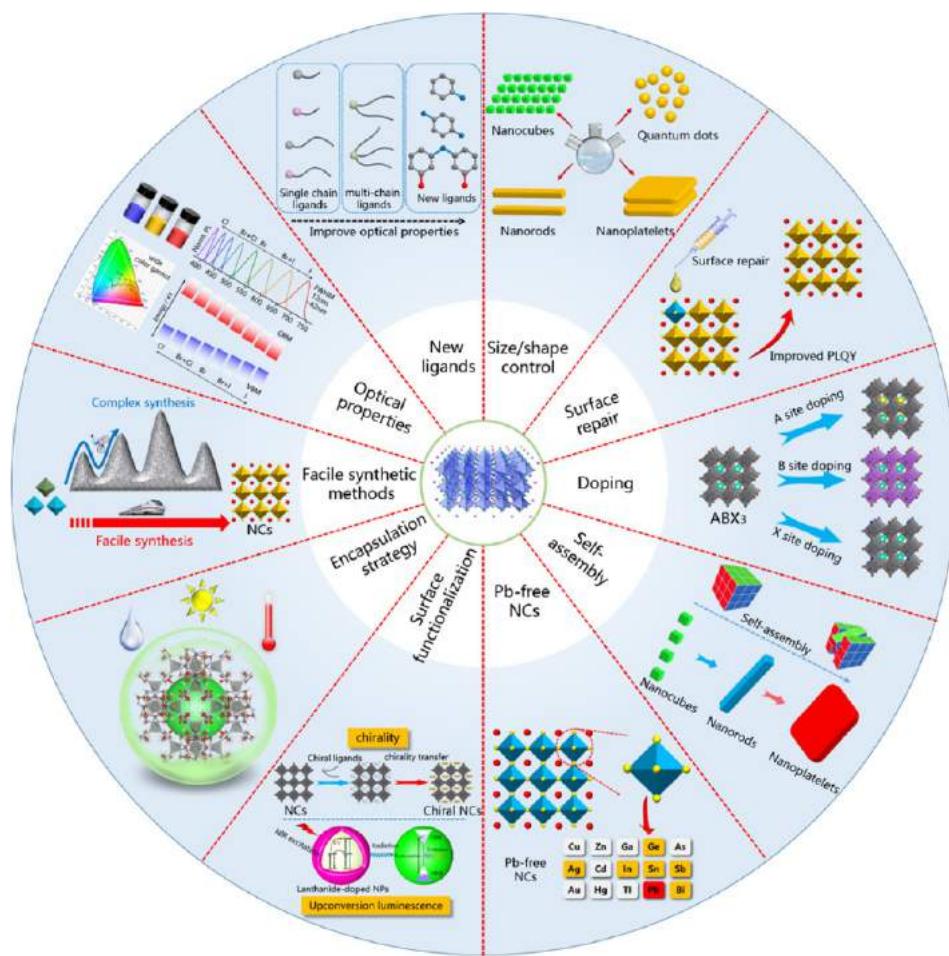


Figure 2. Schematic overview of the current research directions on the chemistry of colloidal MHP NCs.

demonstrated in the latter report and achieved by changing the ratio of the organic cations in LARP, enabled a careful assessment of the quantum-confinement effects in the platelets.¹⁶ Later, the synthesis methodology initially proposed for CsPbX_3 NCs in reference 14 was used also in the early reports on FAPbX_3 ($X = \text{Br}, \text{I}$) and CsFAPbI_3 NCs.^{68,69} After these seminal reports on uniform perovskite NCs, there has been a surge in MHP NC research. Over the years, numerous efforts have been devoted to control the size and shape of MHP NCs by varying the ligands, reaction temperatures, and precursors. A wide range of morphologies such as nanocubes, nanowires (NWs), nanorods (NRs), NPLs, nanosheets (NSs), multifaced nanocrystals,^{70–72} and QDs (nanocubes with sizes in the strong quantum-confinement regime) have been reported.^{18,23,36,48,52,56,73–76} These NCs exhibit either bulk-like (3D) or quantum-confined (2D or 0D) properties depending on their dimensions. For instance, the thickness of the NPLs is precisely tunable down to a single layer of edge-sharing octahedra (Figure 1B, strongly quantum-confined region). Over the years, the syntheses of LHP NCs have been optimized toward monodispersity, with near-unity PLQY and colloidal stability.^{52,77,78} Their size/shape and composition (A, B, and X) are also tunable by post-synthetic shape transformations and ion exchange, respectively.^{52,55,57,73,79} Furthermore, their optical properties are tunable by self-assembly into superlattices.^{80–83} Although low-band-gap, iodine-based MHPs are also defect-tolerant, surface defects caused by the detachment of ligands and surface atoms (B and

X) can strongly affect their PLQYs.^{60,84} To overcome these effects, post-synthetic surface treatment methods have been developed.^{52,60,85,86} In general, a post-synthetic treatment of LHP NCs with ligand molecules or metal halides leads to a significant improvement in their PLQY.^{60,84,87,88} Additional properties could be achieved in perovskite NCs by post-synthetic treatments with functional molecules. The controlled synthesis of LHP NCs makes it easy for the researchers to test these fascinating NCs as active materials in a wide range of applications, including LEDs,⁴⁰ lasers,⁸⁹ solar cells,^{90,91} photo-detectors,³⁷ transistors,^{92,93} and for photocatalysis.⁴³ On the other hand, despite the rapid progress in various aspects of LHP NCs, their stability is one of the major roadblocks in advancing the field toward real-world applications. To address this issue, researchers have implemented both *in situ* synthesis as well as post-synthetic surface coating strategies,^{41,94} but by these approaches, the perovskite NCs are often protected with a layer of organic ligands, acting as a dielectric surface coating, which is a major concern for the injection and transport of charge carriers. Therefore, perovskite NCs coated with dielectric shells can only be used as down-converters in LEDs. Another major obstacle for applying LHP NCs in consumer products such as LEDs and solar cells is the toxicity of lead. Therefore, researchers have been testing various other metals to replace this lead with less toxic alternatives. The replacement of divalent Pb^{2+} with trivalent Bi^{3+} or Sb^{3+} leads to the formation of vacancy ordered triple perovskites ($\text{A}_3\text{B}_2\text{X}_9$), which have a 0D or 2D structure, with exciton binding energies

higher than those of the 3D perovskites.^{95–97} On the other hand, the perovskite crystal structure can be preserved by adding a monovalent B-site cation, as well (e.g., Ag), which leads to the formation of double perovskites, as illustrated in Figure 1C, which have been facing their own challenges in terms of wide band gaps and low PLQYs thus far.

As illustrated in Figure 2, currently, MHP NCs are undergoing further chemical engineering in connection with shape-controlled synthesis using different precursors and ligands, surface functionalization to induce additional functionality (for example, chirality), metal-ion doping, and search for Pb-free NCs alternatives, phase stability (thermal and moisture), and self-assembly. All of these research lines are aimed toward improving and stabilizing their optical properties. Over the years, numerous excellent reviews have been published on MHP NCs, regarding their colloidal chemistry, optical properties (linear and nonlinear), and potential applications.^{21–23,36,37,41,46,52,92–94,98–116} However, there is no extensive literature review covering the entire spectrum of research into aspects of MHP NCs, from synthesis and fundamental properties to device applications and related challenges. It has already been over 5 years since MHP NC research has started, and it has quickly emerged as an important field in contemporary nanoscience and nanotechnology, a field that is still rapidly growing. We have therefore identified the need for a comprehensive literature review on current research lines and future prospects of MHP NCs, not only to guide currently active researchers of this field but also to inspire a younger generation of researchers to join this exciting research field. To realize this, we have put together our expertise to provide a broad overview of currently available knowledge on various aspects of MHP NCs. This review article provides comprehensive and up to date developments in the synthetic methods for the shape-controlled synthesis of MHP NCs (both Pb and Pb-free), their surface chemistry, post-synthetic surface passivation, surface functionalization, self-assembly, and optical properties along with potential applications.

We have organized this review into 11 main parts. (1) Colloidal synthesis of LHP NCs includes a brief history of colloidal synthesis of LHP NCs and a discussion on general approaches developed over the years for their shape/size-controlled (nanocubes, nanoplatelets and nanowires) synthesis and post-synthetic ion exchange for compositional tuning, along with post-synthetic shape transformations. We also discuss *in situ* synthesis approaches to obtain LHP NCs on a substrate. (2) Surface chemistry and post-synthetic surface treatment of LHP NCs improves their optical properties and provides our current understanding of ligand chemistry on LHP NC surface and passivation. (3) We discuss recent advances on 0D Cs_4PbBr_6 NCs, regarding their syntheses, phase transformations and origin of their green photoluminescence. (4) Surface coating strategies are used to enhance the stability of LHP NCs toward humidity, heat and harsh environments. (5) We then discuss various possible metal combinations to synthesize Pb-free perovskite NCs. (6) We provide a summary of LHP NCs doped (A- and B-sites) with various other metal ions to improve their optical properties as well as their phase stability. Special emphasis is paid to Mn^{2+} -doped LHP NCs. (7) We provide a summary of self-assembly strategies employed for the fabrication of LHP nanocube superlattices. (8) We discuss the characterization of LHP NCs and their assembly by TEM and X-ray scattering

techniques. In this section, we describe the challenges associated with characterization of LHP NCs by TEM due to electron-beam-induced degradation. In addition, we discuss X-ray scattering analysis of LHP NC degradation. (9) We discuss the optical properties of MHP NCs, such as their PL, quantum-confinement effects, chirality, and ultrafast charge carrier dynamics. (10) We also discuss the optical studies of quantum dots and nano- and microcrystals at the single-particle level. (11) In the last section, we offer an up to date research progress on various potential applications of MHP NCs, including lasers, LEDs, photodetectors, field-effect transistors (FETs), photovoltaics, and photocatalysis. In addition, an outlook is provided at the end of each section, along with an overall outlook at the end of the article.

SHAPE-CONTROLLED SYNTHESIS OF MHP NCs

Evolution of Different Synthesis Methods. The success of colloidal MHP NCs has resided mainly in the ability to synthesize them with excellent control over their shape, size, and composition, as well as with high quality.^{14,22,23,36,47,52,85,98,105,117} Part of this success stems from the fact that these systems, as soon as they were approached, had largely benefited from the knowledge on conventional colloidal nanocrystals that had accumulated over the past few decades, especially on their synthesis, the study of their fundamental properties, and their device applications.^{58,118–124} On the other hand, MHPs have been known for a very long time, but their connection with the NC world has come only in relatively recent times. As a matter of fact, the fabrication and optical properties of layered MHPs were reported long before (in the 1990s) the realization of their great potential for applications in devices, especially for photovoltaics.^{125–128} Along the line of conventional colloidal QD photovoltaics (PVs), Im *et al.* explored MAPbI_3 NCs in a TiO_2 matrix as a potential sensitizer for PVs in 2011.¹²⁹ In their work, the NCs were synthesized on a nanocrystalline TiO_2 surface by spin-coating the perovskite precursor solution. This was probably one of the early works to inspire the colloidal chemistry research community to investigate the solution-phase synthesis of colloidal MHP NCs. In 2014, Schmidt *et al.* reported the synthesis of MAPbBr_3 perovskite nano/microcrystals.⁶⁶ Their synthesis relied on the use of medium-length alkyl chain organic ammonium cations (octylammonium bromide and octadecylammonium bromide) as capping ligands to obtain colloidal MAPbBr_3 NCs *via* the solvent (acetone)-induced reprecipitation of MABr and PbBr_2 precursors. The prepared MAPbBr_3 nano/microcrystals exhibited green emission with a PLQY of ~20%. The ligands played a critical role in limiting the crystallization to obtain colloidal NCs, as otherwise the precursors would precipitate out to form non-emissive or (weakly emissive) large bulk crystals. Interestingly, a similar concept had been employed previously to obtain 2D-layered halide perovskites on substrates and perovskite colloidal dispersions.¹³⁰ In a subsequent work, Gonzalez-Carrero *et al.*²⁵ further improved the PLQY of these NCs to 83% by optimizing the ligand concentration. However, the morphology of the perovskite colloids was unclear until the colloidal synthesis of well-defined CsPbX_3 NCs reported by Protesescu *et al.* in 2015.¹⁴ They synthesized the CsPbX_3 NCs by adapting a hot-injection strategy (Figure 3). Interestingly, HI has been used for more than two decades for CdSe ⁵⁸ and since then also for other conventional colloidal NCs (Pb chalcogenides, In pnictides, etc.).

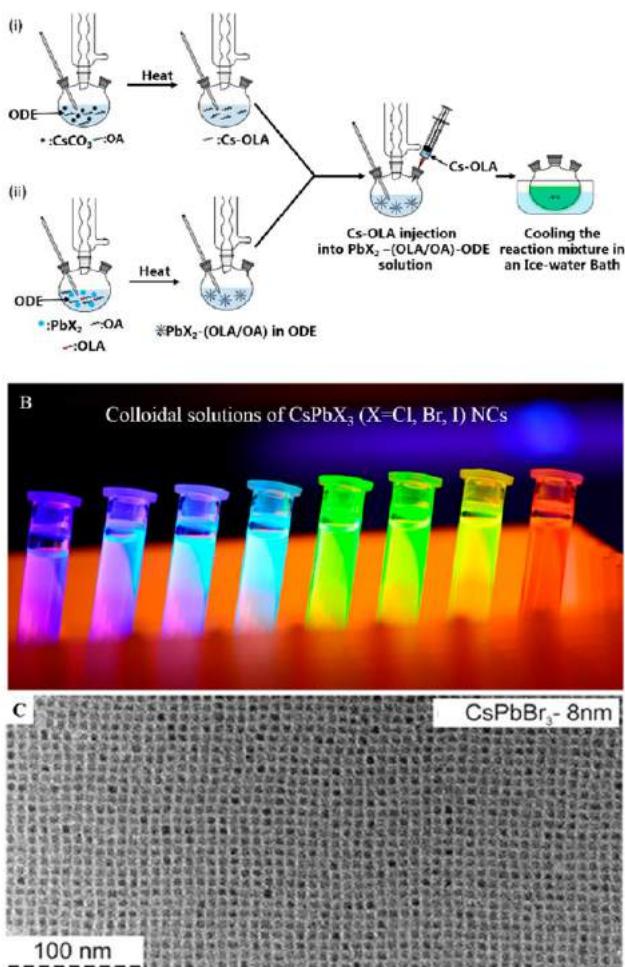


Figure 3. (A) Schematic illustrations of HI synthesis of colloidal CsPbX_3 NCs. The synthesis relies on the injection of presynthesized Cs-oleate into a reaction solution (PbX_2 dissolved in 1-octadecene using oleylamine and oleic acid) at high temperature. (B) Photographs of the colloidal solutions of CsPbX_3 NCs synthesized by the HI method. Photo courtesy of Dr. Loredana Protesescu. (C) TEM images of the corresponding CsPbBr_3 NCs. Panel C is reprinted from ref 14. Copyright 2015 American Chemical Society. Further permissions related to the material excerpted should be directed to the ACS.

Protesescu *et al.* were able to tune the size of the NCs by varying the reaction temperature and thus explored the quantum size effects in this class of NCs. This work lays the foundation for the shape-controlled synthesis of MHP NCs. This pioneering work clearly highlighted that LHP NCs have narrow emission spectra width with high PLQYs (up to 90%), and the PL peak position is precisely tunable across the visible spectrum (400–700 nm) of light by varying the halide (Cl, Br, I) composition and NC size (Figure 3). It is significant that LHP NCs, unlike conventional colloidal semiconductor QDs, exhibit such high PLQYs without any surface passivation. Later in 2015, Sichert *et al.*¹⁶ demonstrated the synthesis of organic–inorganic hybrid perovskite NPs with thickness control down to a monolayer by varying the ratio of long and short-chain ligands in the reprecipitation reaction. For such thin NPs, the quantum-confinement effects strongly affected their absorption and PL properties. The outstanding optical properties of both organic–inorganic and all-inorganic LHPs unveiled by these

initial reports have greatly attracted the interest of researchers from various disciplines.

Over the last few years, significant efforts have been devoted to developing facile and reliable synthesis methods for MHPs. As schematically illustrated in Figure 4, these methods can be mainly classified into either “bottom-up” or “top-down” approaches based on the growth process.^{131,132} The bottom-up approaches can be further subclassified into three different categories based on the nature of the synthesis: (1) heat-up, (2) reprecipitation, and (3) *in situ* synthesis. Among all the strategies illustrated in Figure 4, HI and LARP have been the most frequently used methods for the synthesis of MHP NCs. As illustrated in Figure 3A, the HI synthesis of CsPbX_3 NCs generally relies on the injection of presynthesized Cs-oleate into a reaction mixture containing PbX_2 ligands in 1-octadecene at high temperatures and inert atmospheres, followed by immediate quenching of the reaction with an ice bath.

This method generally produces high-quality monodisperse CsPbX_3 NCs with high PLQY, and this can also be adapted to the synthesis of Pb-free perovskite NCs using suitable precursors (refer to **NANOCRYSTALS OF LEAD-FREE PEROVSKITE-INSPIRED MATERIALS**). Over the years, the HI synthesis of MHP NCs has undergone further optimization with different precursors and ligands to achieve better stability and shape control. However, this method is tedious and requires high temperatures and inert atmospheres, which limits cost-effective mass production. Alternatively, researchers have adapted a few other methods such as tip sonication,³⁰ microwave irradiation,¹³³ ball-milling,¹³¹ and solvothermal methods¹³⁴ for the synthesis of MHP NCs at atmospheric conditions. These are single-step bottom-up synthesis approaches, in which all the precursors and ligands are mixed in a solvent and then reacted by applying heat (solvothermal synthesis, which is very similar to HI) or by tip sonication or microwave irradiation at atmospheric conditions. Nevertheless, the temperature in the reaction medium increases during ultrasonication or microwave irradiation, promoting the reaction.

The inherent ionic nature of perovskites has enabled the synthesis of high-quality MHP NCs by the LARP approach in ambient atmosphere at room temperature. The reprecipitation approach has been known for centuries, and it has been used to prepare organic nanoparticles.^{135–137} This approach relies on the spontaneous crystallization of substances upon reaching a supersaturated state, which can be achieved by lowering the temperature, by solvent evaporation, or by the addition of a poor solvent in which the solubility of the substance is low. If this is carried out in the presence of ligands, nucleation and growth of the precipitate can be controlled, and this is called the LARP process. In early 2015, Zhang *et al.*²⁹ initially employed this LARP approach to synthesize strongly luminescent colloidal MAPbX_3 (X = Cl, Br, I) NCs at room temperature. In this approach, a solution of perovskite precursors (such as MAX, FAX, CsX, along with PbX_2) and ligands (alkylamines and alkyl carboxylic acids) dissolved in a good solvent such as dimethylformamide (DMF) or dimethyl sulfoxide (DMSO) is dropped into a poor solvent (such as toluene or hexane), inducing the instantaneous formation of ligand-capped colloidal perovskite NCs (Figure 5A; see movie S1). The LARP approach generally yields either spherical NCs (Figure 5C) or nanoplatelets.^{16,19} The size of the MAPbBr_3 NCs is tunable by varying the temperature at which LARP is

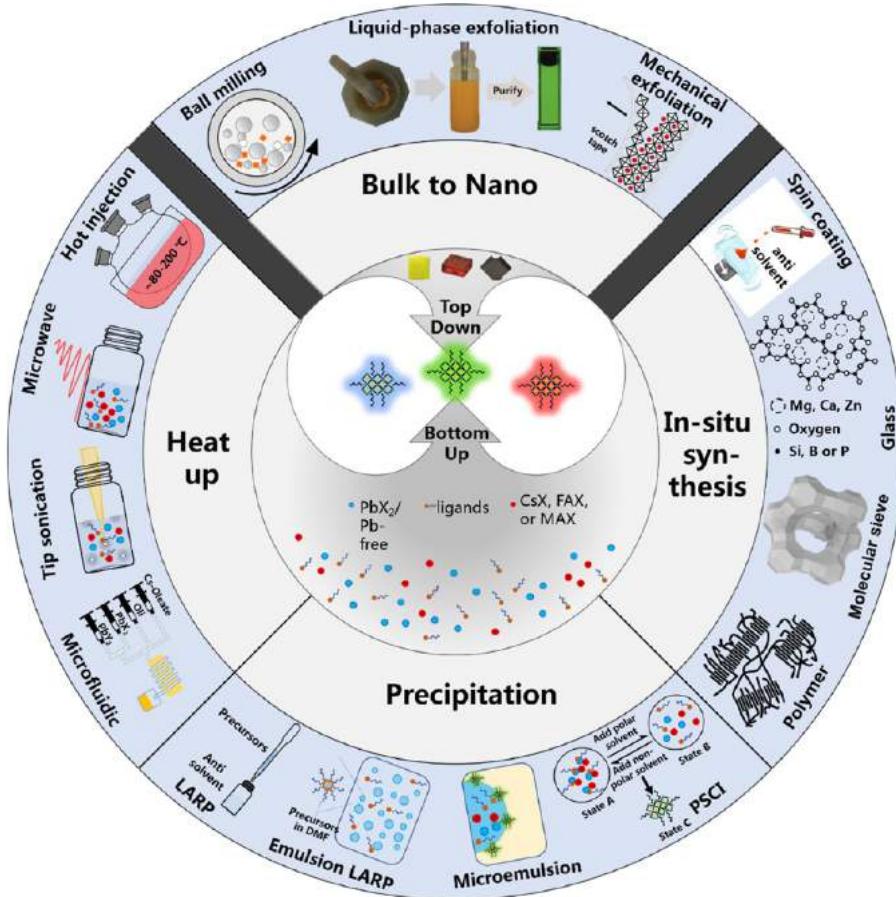


Figure 4. Schematic overview of various synthetic methods for MHP NCs. These methods can be generally classified into either “top-down” or “bottom-up”. The bottom-up methods can be further classified into three different subcategories (heat-up, precipitation, and *in situ* synthesis) depending on the type of reaction. PSCI, polar solvent-controlled ionization; LARP, ligand-assisted reprecipitation.

carried out, as shown by Huang *et al.*¹³⁸ Yet, there is still a debate on whether the spherical NCs are perovskites or Pb clusters that result from electron-beam-induced degradation of perovskite NCs (movie S2).^{16,30,139} The LARP approach has been further updated into emulsion synthesis, which enabled the purification of MAPbBr_3 NCs by precipitation into solid-state light-emitting powder form.¹³⁸ This can be redissolved into solvents for processing thin-film devices.^{140,141} This LARP approach has also been extended to all-inorganic MHP NCs.^{53,77} However, the level of shape control achieved by LARP is still lagging far behind that of the HI synthesis. As illustrated in Figure 2, currently, the synthesis of MHP NCs is undergoing further fine-tuning in connection with shape control using different precursors and ligands, surface functionalization to induce additional functionalities (for example, chirality), and metal-ion doping, moving the focus toward Pb-free NCs, phase stability (thermal and moisture), and self-assembly. All these research lines are aimed toward improving the optical properties of NCs or finding alternative, less toxic compositions while keeping optical performances high. Despite significant advances in the synthesis of MHP NCs, only limited shape control has been achieved, as mainly NCs, NPs, and NWs have been frequently reported. In the following, we discuss the state of the art synthesis of these three morphologies.

Nanocubes. Nanocubes are the most explored MHP NCs in terms of their synthesis, characterization, and investigation for potential applications.^{14,52,53,89,142} Over the last 5 years,

there has been significant progress toward the development of reliable and scalable synthetic approaches for MHP nanocubes with tunable composition and high PLQY.^{14,30,52,53,134,143,144} As a result, these nanocubes have already shown great promise for LEDs, lasers, and solar cells, as compared with other MHP morphologies and nanostructures.^{42,89,90,142} In general, perovskite precursors often tend to precipitate to form NCs with cubic shapes at high reaction temperatures, while they tend to crystallize into nanoplatelet morphologies at relatively low reaction temperatures. This temperature dependence is now better understood in terms of acid/base equilibria regulating the protonation/deprotonation of the alkylamine ligands used in the synthesis competing with Cs^+ ions for their inclusion to the facets of the growing NCs.¹⁴⁵ In fact, CsPbX_3 perovskite nanocubes were initially synthesized using a well-known HI method, and it is still the most frequently used method to synthesize MHP NCs (Figure 3 and movie S3: large-scale synthesis of CsPbBr_3 nanocubes; the hot injection is realized here by creating a reduced pressure in the flask and opening the valve of the dropping funnel).¹⁴ In this method, PbX_2 precursors were first dissolved in octadecene, followed by the injection of Cs-oleate at high temperature and inert atmosphere. It is worth mentioning that the reaction has to be quickly quenched with an ice bath upon the injection of Cs-oleate; otherwise, a prolonged reaction time leads to the formation of nanowires as side products (the reader should consult the nanowires section for additional details).⁷⁵ This method generally yields monodisperse CsPbX_3 nanocubes, and

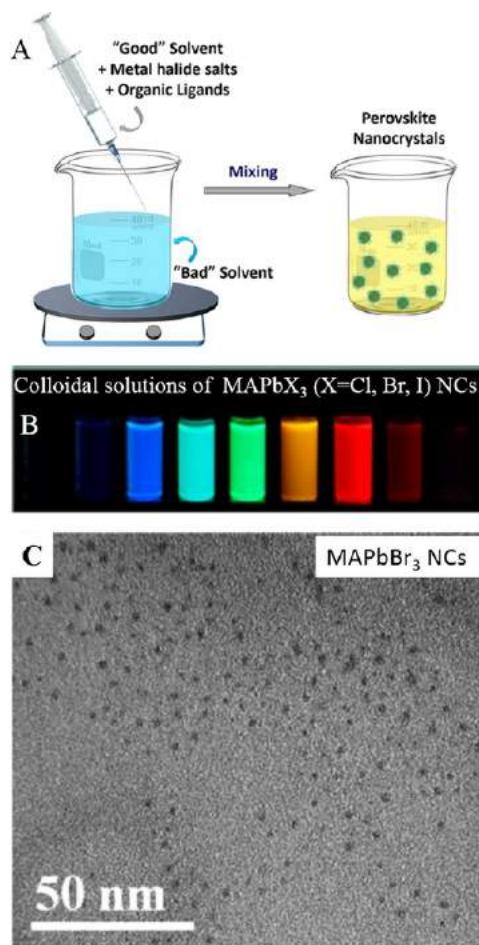


Figure 5. (A) Schematic illustrations of the synthesis of colloidal MAPbX_3 NCs by the LARP approach. Reprinted from ref 52. Copyright 2019 American Chemical Society. Further permissions related to the material excerpted should be directed to the ACS. The synthesis relies on dropping precursor powders and ligands dissolved in a good solvent (such as DMF or DMSO) into a poor solvent (such as toluene or hexane). (B) Photographs of the colloidal solutions of MAPbX_3 NCs synthesized by the HI method. (C) TEM images of the corresponding MAPbBr_3 NCs. Panels B and C are reprinted from ref 29. Copyright 2015 American Chemical Society.

the halide composition of the nanocubes is easily tunable by varying the ratio of PbX_2 precursors in the reaction medium. Although the initial studies suggested that these CsPbX_3 nanocubes exhibit cubic structures,^{14,30,53} CsPbBr_3 nanocubes were later found to have an orthorhombic crystal structure.^{143,146,147} The Br- and I-based perovskite NCs generally feature high PLQY (near-unity has been reported), while the Cl-based NCs suffer from lower PLQYs.^{14,30,57} Nevertheless, recent studies have shown that post-synthetic treatment with metal chloride salts can significantly improve the PLQY of CsPbCl_3 nanocubes up to near-unity.^{87,148} However, it is still unclear whether metal ion doping or the surface passivation with chloride ions or both leads to the observed PLQY enhancement.⁸⁶

In addition, the size of the CsPbX_3 perovskite nanocubes is also tunable over a limited range *via* hot-injection synthesis. However, unlike conventional colloidal NCs, the size of the perovskite NCs is tunable by controlling the reaction temperature rather than the growth kinetics because of their

fast (1–3 s) nucleation and growth. In general, the size of the perovskite nanocubes decreases with decreasing reaction temperature. For instance, Protesescu *et al.* synthesized monodisperse nanocubes of size range of 4–15 nm by hot-injection synthesis *via* temperature control (140–200 °C).¹⁴ Nevertheless, it should be noted that precursors crystallize into nanoplatelets at low reaction temperatures (<130 °C).¹⁸ For precise control over the size of quantum-confined CsPbX_3 nanocubes, Dong *et al.*¹⁴⁹ proposed a strategy based on the halide ion equilibrium between the nanocubes and the reaction medium, along with temperature control (Figure 6). In principle, the halide (X) to Pb ratio should be higher for small (strongly quantum-confined) CsPbX_3 nanocubes. As the Br^- ions diffuse in and out of the crystal lattice with a low kinetic barrier, the size of the resulting nanocube depends on the variation of the Br^- equilibrium between the nanocube and the reaction medium. Therefore, at a given temperature, the increase in the Br/Pb ratio for a fixed amount of Cs^+ and Pb^{2+} in the reaction medium leads to a decrease in the nanocube size (Figure 6A). Similarly, for a fixed Br/Pb ratio, the size of the nanocube decreases with decreasing reaction temperature (Figure 6A). This model was proposed based on the Br^- equilibrium between the nanocube lattice and the reaction medium and is consistent with the experimentally observed (from TEM analysis shown Figure 6A) correlation between nanocube size and Br/Pb ratio (Figure 6B). This method has received considerable attention regarding the preparation and study of the optical properties of size controlled quantum-confined nanocubes.^{150–153} In addition, several other potential methods have also been reported for the growth of size-controlled quantum-confined CsPbBr_3 nanocubes.^{79,145,154} For instance, Pradhan and co-workers showed that the size of the CsPbBr_3 nanocubes can be reduced down to ~3.5 nm by increasing the amount of oleylamine–HBr (OLA–HBr) in the reaction medium at a fixed temperature (160 °C).⁷⁹ To achieve a better understanding of the role of ligands (OLA and OA) in controlling the shape and size of perovskite NCs, Almeida and co-workers performed a systematic synthetic study by varying the ratio between OLA and OA and correlated with the size, shape, and distribution of the resultant CsPbBr_3 NCs.¹⁴⁵ They found that a high concentration of oleylammonium species in the reaction medium leads to the formation of nanoplatelets, whereas a low concentration results in nanocubes. In addition, they were able to prepare monodisperse CsPbBr_3 nanocubes with sizes ranging from 4.0 to 16.4 nm by varying the OLA/OA ratio along with reaction temperature. Despite the successful synthesis of small nanocubes (<20 nm), precise control over the size of CsPbX_3 nanocubes with sizes above 20 nm is still challenging.

Although the hot-injection method has been extensively used for the synthesis of inorganic perovskite nanocubes, it is tedious and generally carried out under inert conditions. Moreover, it requires an additional synthesis step for the Cs-oleate precursor. To overcome these limitations, several alternative methods, such as microwave irradiation,¹³³ ultrasonication,³⁰ solvothermal synthesis¹³⁴, and LARP⁵³ have been reported. For instance, Zeng and co-workers reported the early work on the RT synthesis of highly luminescent CsPbX_3 perovskite nanocubes using the LARP method (Figure 7A,B).⁵³ In this method, CsBr and PbBr_2 precursors were first dissolved in DMF or DMSO along with OLA and OA ligands. The precursor solution was then added to toluene at RT to trigger the precipitation of brightly luminescent

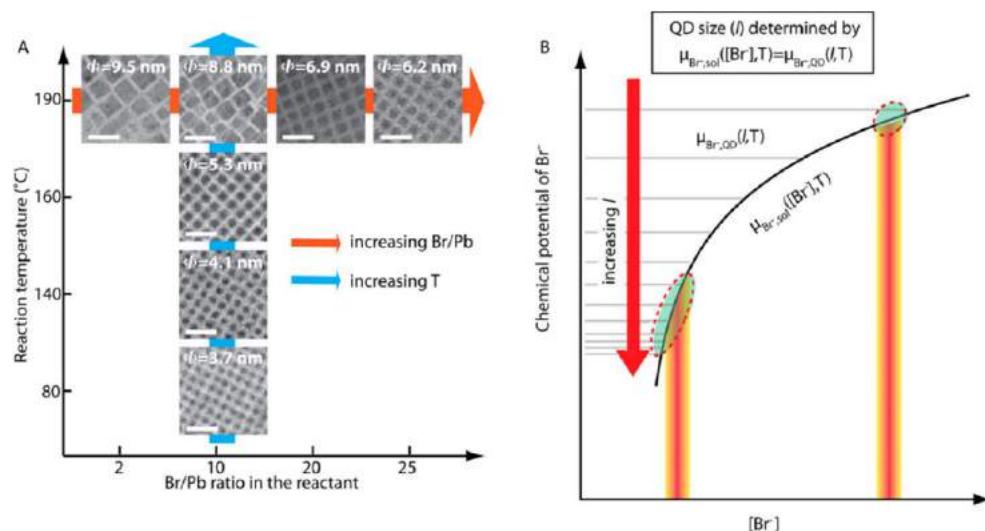


Figure 6. Size control of CsPbBr₃ perovskite nanocubes *via* thermodynamic equilibrium in hot-injection synthesis. (A) Dependence of the size of CsPbBr₃ nanocubes on the Br to Pb ratio in the reaction medium and the reaction temperature. (B) Proposed model illustrating the determination of the nanocube size *via* equilibrium of Br⁻ between the nanocube lattice and the reaction medium. The nanocube size for a given concentration of Br⁻ ([Br⁻]) and temperature (T) is determined at which the chemical potentials (μ_{Br^-}) of Br⁻ in the reaction medium become equal. The inverse correlation between the nanocube size and the concentration of Br⁻ at a given temperature (T) can be clearly seen from the two marked (dotted circles) areas. Reproduced from ref 149. Copyright 2018 American Chemical Society.

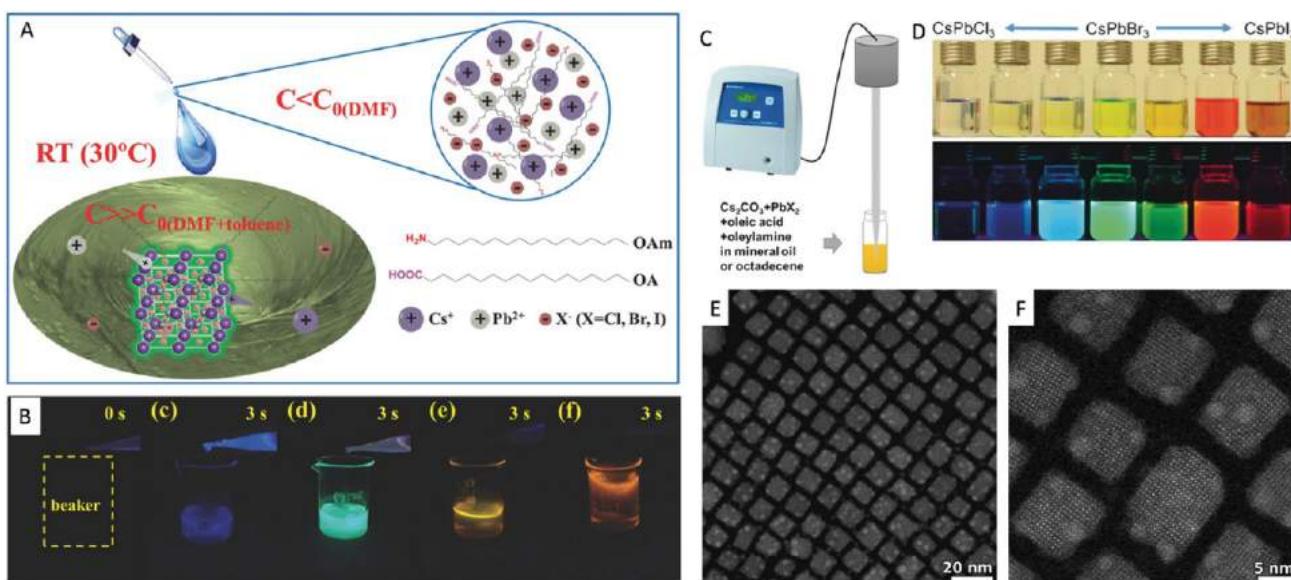


Figure 7. Highly luminescent CsPbX₃ (X = Cl, Br, and I) nanocubes *via* supersaturated recrystallization at RT and single-step ultrasonication approaches. (A) Schematic illustration of the RT synthesis of CsPbX₃ nanocubes. The precursors (Cs⁺, Pb²⁺, and X⁻ ions) crystallize into perovskite nanocubes under ambient conditions within 10 s after having been transferred from a good solvent (DMF) to a bad solvent (toluene). (B) Photographs of pure toluene (0 s) and the colloidal solutions of CsPbX₃ nanocubes with different halide compositions formed within 3 s after the injection of corresponding DMF precursors into pure toluene under UV illumination in darkness. Panels A and B are reprinted with permission from ref 53. Copyright 2016 John Wiley & Sons, Inc. (C) Schematic illustration of the single-step synthesis of CsPbX₃ perovskite nanocubes. (D) Photograph of the colloidal dispersions of CsPbX₃ NCs with different halide (X = Cl, Br, and I) compositions under room light (top) and UV light (bottom). (E,F) Different magnification high-angle annular dark-field scanning transmission electron microscopy images of CsPbBr₃ nanocubes obtained by ultrasonication approach. Panels C and D are adapted from ref 30. Copyright 2016 John Wiley & Sons, Inc.

perovskite nanocubes within a few seconds, as shown in Figure 7B. The authors reported a PLQY of 95% for CsPbBr₃ nanocubes prepared by this method. The emission color was easily tunable by the halide composition in the precursor solution in DMF. Nevertheless, this method required the use of polar solvents that can influence the stability of the prepared NCs. In 2016, Tong *et al.*³⁰ reported the polar-solvent-free

single-step synthesis of CsPbX₃ nanocubes with controllable halide composition by ultrasonication of the precursor salts in the presence of ligands (Figure 7C,D). This is one of the easiest and fastest methods to obtain perovskite NCs. The emission color of the prepared nanocubes is easily tunable by varying the ratio of different halide precursors in the reaction medium. The nanocubes prepared by this approach are nearly

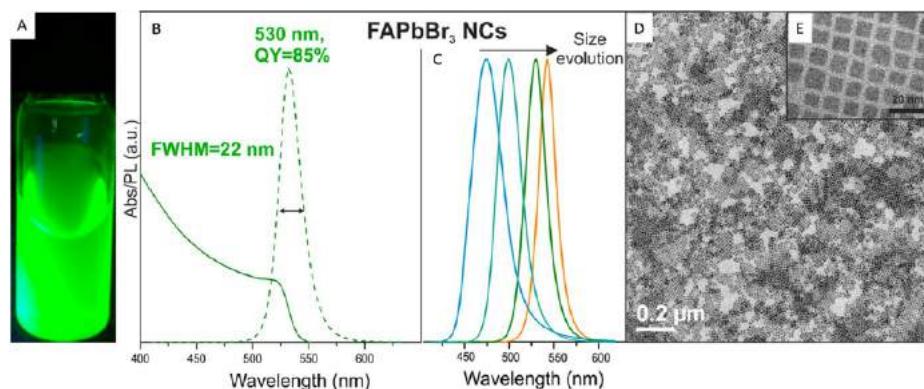


Figure 8. Synthesis of FAPbBr_3 nanocubes by hot injection. (A) Photograph of colloidal solution of FAPbBr_3 nanocubes in toluene under UV light illumination. (B) UV-vis absorption and PL spectra of FAPbBr_3 nanocubes with a PL peak maximum at 530 nm. (C) PL spectra for FAPbBr_3 NCs of different sizes. The emission peak red shifts with increasing size from 5 to >50 nm. (D,E) TEM images of FAPbBr_3 nanocubes at two different magnifications. Reproduced from ref 68. Copyright 2016 American Chemical Society. Further permissions related to the material excerpted should be directed to the ACS.

monodisperse and exhibit high PLQY. This method was further extended to the preparation of perovskite nanowires²² and nanorods.¹⁵⁵ In 2017, Chen *et al.* reported the solvothermal synthesis CsPbX_3 NCs.¹³⁴ In this method, the precursors and ligands were loaded in a Teflon-lined autoclave and then heated at 160 °C for 30 min. The obtained nanocubes appeared to be rather monodisperse with a PLQY up to 80%. Zhai *et al.* further extended this method to CsPbBr_3 nanoplatelets using presynthesized Cs-oleate as the precursor.¹⁵⁶

In comparison to the many studies on inorganic perovskite NCs, organic–inorganic hybrid perovskite nanocubes have been rarely reported.^{68,157–161} In 2016, Vybornyi *et al.*¹⁵⁸ demonstrated a polar-solvent-free colloidal synthesis of MAPbBr_3 perovskite NCs by the HI method. They were able to tune the morphology from nanocubes to nanoplatelets and nanowires by varying the reaction parameters. In 2019, Zhang *et al.* extended this method to the synthesis of monodisperse MAPbI_3 nanocubes.¹⁶⁰ The main problem associated with these MA-based perovskites is their chemical decomposition, which limits their applications. Alternatively, Protesescu *et al.*⁶⁸ reported stable and bright green emissive FAPbBr_3 nanocubes by the hot-injection method (Figure 8). In this method, FA and Pb acetate precursors were first dissolved in octadecene in the presence of OA, followed by the injection of presynthesized oleylammonium bromide (OLABr) at 130 °C. This method is slightly different from the typical hot-injection method used for the synthesis of CsPbX_3 NCs, where PbBr_2 was used as precursor for both Pb and Br. This hot-injection method, in which FA-oleate was injected into PbBr_2 –OA–OLA solution, produced FAPbBr_3 nanocubes with a much broader size distribution. The nanocubes prepared by this method are rather monodisperse (12 nm) with the PL peak at 530 nm and QY of 85% (Figure 8B). In addition, the authors demonstrated that the size of the FAPbBr_3 nanocubes can be tuned from 5 to 50 nm by adjusting either the amount of OLABr or the reaction temperature, and thus the emission peak is tunable from 470 to 545 nm (Figure 8C).⁶⁸ The purification process after the synthesis of perovskite NCs is critical in order to recover monodisperse NCs. Very recently, Li *et al.*¹⁶² proposed size-selective precipitation using a mixture of ethyl acetate and methyl acetate (2:1 volume ratio) to obtain strongly confined

nanocubes of different sizes. The precipitation process can be repeated multiple times to obtain FAPbBr_3 nanocubes of different sizes. Hybrid perovskite NCs have also often been prepared by the LARP method, and the resulting NCs possess either spherical or nanoplatelet morphology.^{29,66} However, there is still debate on whether the spherical particles obtained by the LARP method are perovskites or whether they are the e-beam-induced degradation product of perovskite NPs (see Electron Microscopy section). In 2017, Levchuk *et al.*¹⁵⁹ reported the RT synthesis of brightly luminescent FAPbX_3 nanocubes by the LARP method. The synthesis relies on the rapid injection of a precursor solution (PbX_2 and FAX dissolved in DMF along with OA and OLA) into chloroform. The obtained nanocubes exhibit PLQYs up to 85%. They were able to tune the morphology from nanocubes to NPs of different thicknesses by varying the OLA/OA ratio. However, the cubic morphology of the particles obtained in this approach is not as perfect as that of the nanocubes synthesized by the hot-injection method. A few months later, Minh *et al.*¹⁶³ reported a RT synthesis of FAPbX_3 nanocubes by LARP method, in which presynthesized PbX_2 –DMSO complexes were used as precursors. In this approach, the precursors (FAX and PbX_2 –DMSO complex) were first dissolved in DMF along with OLA, followed by injection of the precursor solution into a mixture of toluene and OA. They were able to tune the size distribution of the nanocubes by varying the amount of OLA used in the reprecipitation reaction. The quality of the nanocubes prepared by this approach appeared to be as good as that of the nanocubes prepared by hot injection. Such a purification approach is also useful for the size-selective separation of inorganic perovskite nanocubes, as demonstrated by Forde *et al.*¹⁵⁴ Very recently, Zu *et al.* reported the synthesis of FAPbBr_3 NCs by the LARP approach using sulfobetaine-18 (SBE-18) as the capping ligand.¹⁶⁴ The authors claimed that the FAPbBr_3 nanocubes prepared using SBE-18 ligands (PLQY $\approx 90.6\%$, $\text{fwhm} \approx 20.5$ nm) exhibited PLQYs (as well as green color purity) higher than those of OLA/OA-capped FAPbBr_3 nanocubes (PLQY $\approx 83.2\%$, $\text{fwhm} \approx 24$ nm) prepared under similar conditions.

In general, capping agents play a critical role in controlling the shape of NCs during colloidal synthesis, the properties of the NCs, as well as their colloidal stability.^{165–167} Recently, there has been a growing interest in the exploration of different

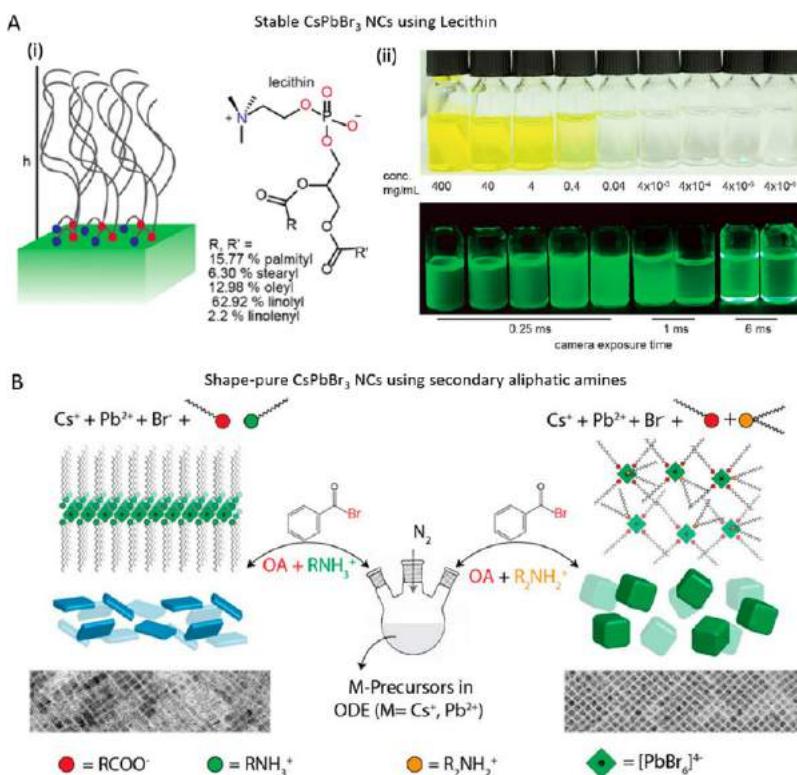


Figure 9. (A) Schematic illustration showing the synthesis of CsPbBr_3 NCs using primary (left) and secondary (right) aliphatic amines. The TEM images showing the resultant products in the respective reactions. Reproduced from ref 170. Copyright 2019 American Chemical Society. Further permissions related to the material excerpted should be directed to the ACS. (B) (i) Schematic of lecithin ligands forming a brushlike structure on the NC surface, and the “h” indicates the brush height (left) and chemical structure of lecithin and statistical occurrence of side chains (R, R') in soy lecithin (right). (ii) Photographs of the colloidal solutions of lecithin-capped CsPbBr_3 NCs at various concentrations under daylight (top) and UV light (bottom). Reproduced from ref 143. Copyright 2018 American Chemical Society. Further permissions related to the material excerpted should be directed to the ACS.

ligands for shape-controlled synthesis and stability of perovskite NCs with high PLQYs.^{168–174} For instance, in 2017, Liu *et al.*¹⁷⁵ reported the use of trioctylphosphine– PbI_2 (TOP– PbI_2) as a precursor for the synthesis of phase-stable CsPbI_3 nanocubes with near-unity PLQY. Their approach relies on the injection of presynthesized TOP– PbI_2 precursor into a reaction mixture containing Cs_2CO_3 , OA, and OLA in octadecene (ODE) at different temperatures that are set to achieve a desired size for nanocubes. The authors found that these CsPbI_3 nanocubes exhibited higher stability as well higher PLQY compared to those of the nanocubes prepared without the use of the TOP ligand. The higher PLQY was attributed to the removal of nonradiative traps upon strong binding of TOP to the nanocube surface. Around the same time, Wu *et al.*¹⁶⁹ further showed that the incorporation of a highly branched capping ligand, trioctylphosphine oxide (TOPO), along with traditional oleic acid/oleylamine ligand, leads to monodisperse CsPbX_3 nanocubes at high temperature (260 °C). Otherwise, the reaction led to large aggregates at such temperatures in the absence of TOPO. More importantly, the authors found that the TOPO-protected CsPbBr_3 nanocubes exhibited superior stability in ethanol as compared to that of OA/OLA-capped CsPbBr_3 nanocubes, regardless of the reaction temperatures at which they were synthesized. The most important factor in the selection of ligands is that they should bind strongly to the NC surface so that they do not detach during the washing process. However, this is not the case for OA/OLA-capped perovskite NCs, as their optical

properties and applications are often hampered by the colloidal and structural instability caused by the desorption of ligands. To address this issue, Krieg *et al.*¹⁷¹ proposed zwitterionic capping ligands to enhance the stability and durability of CsPbBr_3 nanocubes, and the authors named the corresponding NCs as “ CsPbX_3 (X = Cl, Br, I) nanocrystals 2.0”. The Cs and Pb precursors used in their synthesis are different from the ones used in the hot-injection synthesis of OA/OLA-capped CsPbX_3 NCs. The synthesis used by Kreig *et al.* is based on the injection of presynthesized TOP-X₂ into a mixture of presynthesized Cs-2-ethylhexanoate solution, Pb(II)-ethylhexanoate solution, and zwitterionic ligand (3-*N,N*-(dimethyloctadecylammonio)propanesulfonate) at 160 °C. Interestingly, the authors claimed that the morphology and optical properties of these nanocubes were preserved after several washing cycles. The enhanced stability of zwitterionic ligand-capped CsPbX_3 NCs was attributed to the simultaneous coordination of each ligand molecule to the surface cations and anions of NC. In a subsequent work, the same group introduced another zwitterionic capping ligand, namely, soy-lecithin, a mass-produced natural phospholipid, to protect the surface of CsPbX_3 (X = Cl, Br) nanocubes through tight binding to the cations and anions at the surface (Figure 9A-i).¹⁷⁰ The ligand enabled the high-yield synthesis of CsPbX_3 nanocubes with a long-term colloidal and structural stability in a broad range of colloidal concentrations (from a few mg mL⁻¹ to >400 mg mL⁻¹), as shown in Figure 9A-ii. They attributed such high colloidal stability to an increased particle–particle

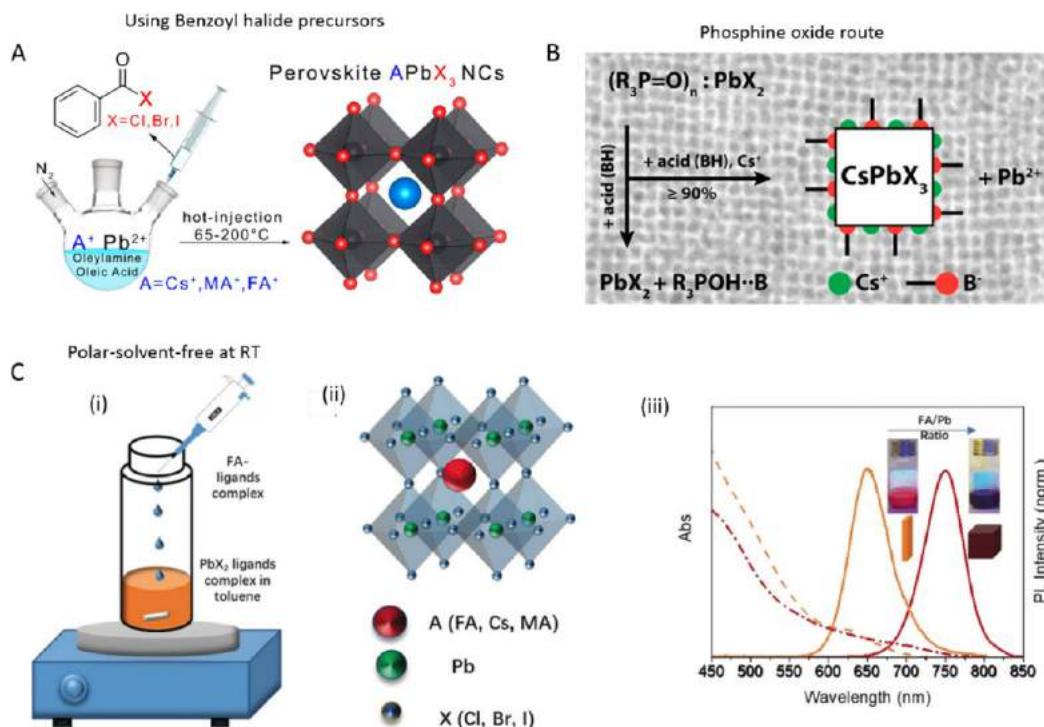


Figure 10. Reaction schemes of the colloidal synthesis of halide perovskite NCs using (A) benzoyl halide precursors. Reproduced from ref 178. Copyright 2018. American Chemical Society. Further permissions related to the material excerpted should be directed to the ACS. (B) trioctylphosphine oxide (TOPO) instead of aliphatic amines. Reprinted with permission under Creative Common [CC-BY] license from ref 179. Copyright 2018 American Chemical Society. (C) Schematic illustration of the polar-solvent-free synthesis of halide perovskite NCs at room temperature by spontaneous crystallization (i) and perovskite crystal structure (ii). The shape of the NCs depends on the precursor ratio (iii). Reprinted with permission under a Creative Commons CC BY license from ref 54. Copyright 2019 John Wiley & Sons, Inc.

repulsion caused by branched chains and ligand polydispersity. In addition, the authors demonstrated the fabrication of micrometer-thick and homogeneous dense CsPbBr_3 nanocube films in a single spin-coating step using ultraconcentrated colloidal solutions. Very recently, Wang *et al.*¹⁷³ demonstrated the potential application of polyzwitterionic ligands for phase transfer of CsPbBr_3 nanocubes from a nonpolar solvent to a polar solvent through ligand exchange. Such polyzwitterionic ligands on the NC surface enabled the stabilization of CsPbBr_3 NCs in a wide range of solvents. These studies suggest that the long-chain molecules with multiple functional groups can serve as potential ligands for perovskite NCs with long-term colloidal stability. A similar ligand binding strategy was applied to obtain stable CsPbI_3 NCs with near-unity PLQY using 2,2'-iminodibenzonic acid as the bidentate ligand.¹⁷²

In addition, several groups showed that the chain length of alkylamines and carboxylic acids ligands plays an important role in the morphology of perovskite NCs.^{143,176,177} For instance, Pan *et al.* systematically studied the influence of the chain length of alkylamine and carboxylic acid ligands used in hot injection.¹⁷⁷ They found an increase in the size of the CsPbBr_3 nanocubes when the chain length of the carboxylic acid was shortened at high reaction temperatures. On the other hand, the replacement of OLA with a short-chain amine leads to a change in the morphology from nanocubes to nanoplatelets. However, it is not uncommon to have a small percentage of nanoplatelets in nanocube samples or *vice versa*. Very recently, Imran *et al.* reported the synthesis of shape-pure, nearly monodisperse nanocubes using secondary aliphatic amine ligands (Figure 9B).¹⁴³ Interestingly, their synthesis yielded only nanocubes, regardless of the length of the alkyl

chains, oleic acid concentration, and reaction temperature. As illustrated in Figure 9B, they proposed that the secondary ammonium ions do not bind to the surface of CsPbBr_3 NCs as effectively as primary ammonium ions (oleylammonium in this case) due to steric hindrance, which limits the formation of nanoplatelets. This was further supported by the fact that the surface coverage (6–8%) of secondary ammonium cations is much lower than that of oleate molecules (92–94%), as revealed by nuclear magnetic resonance (NMR) measurements and X-ray photoelectron spectroscopy (XPS).

Currently, colloidal syntheses of CsPbX_3 NCs are undergoing further optimization using a variety of precursors and ligands, and many general methods are being developed for better control over their shape, composition, and polydispersity.^{54,161,167,179–182} In most synthesis methods that are in use for perovskite NCs, PbX_2 salts are employed as precursors for both Pb and halide ions. This limits the precise control over the reactant species and thus the final chemical composition of colloidal perovskite NCs. To overcome this, Imran *et al.*¹⁷⁸ reported the use of benzoyl halides as the halide precursors for monodisperse APbX_3 NCs (in which $\text{A} = \text{Cs}^+$, CH_3NH_3^+ , or $\text{CH}(\text{NH}_2)_2^+$). Their method relied on the injection of benzoyl halide precursor into the reaction medium containing cesium carbonate (organic cation for hybrid perovskite NCs) and lead acetate trihydrate along with ligands at high temperature (Figure 10A; also note that a similar approach using instead tris-trimethylsilyl bromide or chloride as halide precursor was employed by Creutz *et al.* in the synthesis of double halide perovskite NCs).¹⁸³ This approach enabled one to independently tune the amount of both cations (A^+ and Pb^{2+}) and halide (X^-) precursors in the synthesis. Interestingly, this

method produced nearly monodisperse MAPbX_3 nanocubes, which seems difficult to obtain using other synthesis methods. In addition, the same group developed an amine-free synthesis of CsPbBr_3 nanocubes by complete replacement of the routinely used aliphatic amines with TOPO (Figure 10B).¹⁷⁹ Their synthesis relied on the injection of Cs-oleate into a reaction mixture containing PbBr_2 along with TOPO and OA. This reaction yielded only nanocubes regardless of the tested reaction conditions. This was attributed to the absence of primary amines in the reaction medium. The TOPO helped to dissolve the PbBr_2 in the reaction medium as well as to establish an acid–base equilibrium with OA in a way similar to the OA–OLA system (Figure 10B).¹⁷⁹ Therefore, the acidity of the reaction environment controlled the reactivity of the PbX_2 precursor and thus regulated the size of the NCs. Interestingly, only Cs-oleate ligands were present on the surface of the NCs, and they were bound dynamically to the NC surface; therefore, an optimum concentration of ligands was necessary to achieve high PLQY. Despite achieving excellent control over the shape purity and polydispersity of ABX_3 perovskite NCs, most discussed synthesis methods require inert atmosphere and high temperature. In contrast, Polavarapu and co-workers demonstrated a polar-solvent-free synthesis for ABX_3 NCs at ambient conditions through spontaneous crystallization of precursor–ligand complexes in a nonpolar organic medium (Figure 10C-i).⁵⁴ Furthermore, the shape of perovskite NCs was controllable from nanocubes to nanoplatelets by varying the ratio of monovalent (*e.g.*, formamidinium (FA^+) and Cs^+) to divalent (Pb^{2+}) cation–ligand complexes (Figure 10C-iii). The authors demonstrated the versatility of this method by applying it to perovskite NCs of different compositions.

Isolation and Purification of Colloidal MHP Nanocubes. Colloidal ligand-stabilized NCs are usually extracted from crude reaction mixtures and purified by antisolvent precipitation.⁵⁸ When the capping ligand layer is hydrophobic, a miscible polar solvent is used to flocculate the NCs, which are then isolated by centrifugation. This precipitative washing procedure removes excess ligand, residual reactants, and molecular byproducts and is an important step when the NCs are to be used in devices, such as solar cells or light-emitting diodes that require charge transport through a deposited layer of nanocrystals.

Metal-halide perovskite nanocubes can degrade during the purification process. Bound ligands are in dynamic equilibrium with free ligands, and polar solvents can lower the kinetic barrier to ligand exchange and enhance ligand desorption.⁸⁴ “Overwashing” can lead to irreversible aggregation, changes in morphology, a significant drop in photoluminescence, or even more significantly, changes in crystal phase or composition.^{184,185} For example, perovskite CsPbI_3 nanocubes often transform to the yellow non-perovskite phase,^{185,186} and $\text{CH}_3\text{NH}_3\text{PbI}_3$ (MAPI) nanocubes decompose into PbI_2 .¹⁸⁷

Of course, one way to minimize degradation is to avoid the use of polar solvents, hence simply allowing the nanocubes to settle by centrifuging the crude reaction mixture at high speeds.^{158,181,188} This mostly works, but it often leaves a significant amount of nanocubes suspended in the supernatant, which are then discarded. A considerable residue of unbound ligand and low volatility reaction solvent (*i.e.*, octadecene) is also retained in the nanocube precipitate.^{84,189} This residue is a problem for device applications. It also creates challenges during characterization. TEM is difficult with so much excess

hydrocarbon impurity, and free ligand contamination strongly interferes with the signal from bound ligand in analytical techniques like Fourier transform infrared (FTIR) spectroscopy and NMR spectroscopy.

With some care, a variety of polar antisolvents can be used to precipitate and purify metal-halide perovskite nanocubes without degradation.^{184,185,190} Methyl acetate has been widely used.^{160,185,191–193} Figure 11 shows absorbance and PL spectra

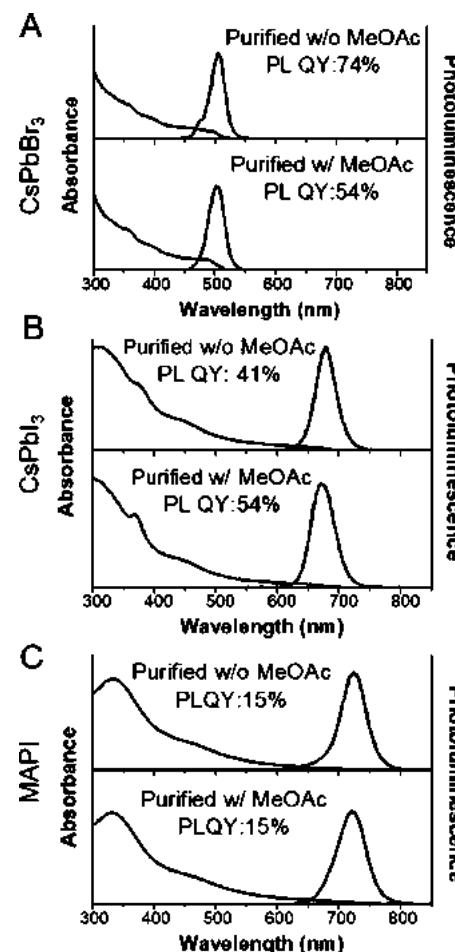


Figure 11. UV–vis absorbance and PL emission spectra of (A) CsPbBr_3 , (B) CsPbI_3 , and (C) MAPI nanocubes in hexane that were isolated from crude reaction mixtures by centrifugation with or without the addition of methyl acetate (MeOAc). The nanocubes were isolated using an equal volume of MeOAc added to the crude reaction mixtures, followed by centrifugation at 8000 rpm (8228g) for 5 min. Poorly capped nanocubes were removed from the sample by dispersing the nanocubes in hexane and centrifuging again at 8500 rpm (9289g) for 5 min. The excitation wavelength was 350 nm for CsPbBr_3 and 470 nm for CsPbI_3 and MAPI nanocubes, and PLQYs were determined relative to Rhodamine-B. Adapted from ref 187. Copyright 2020 American Chemical Society. Further permissions related to the material excerpted should be directed to the ACS.

of CsPbBr_3 , CsPbI_3 , and MAPI nanocubes isolated from reaction mixtures by antisolvent precipitation with methyl acetate. The optical properties of these nanocubes are comparable to those of the nanocubes isolated without methyl acetate. Figure 12 shows images of CsPbBr_3 , CsPbI_3 , MAPI, and $\text{Cs}_2\text{AgBiBr}_6$ nanocubes that were precipitated with methanol, 1-butanol, acetonitrile, acetone, methyl acetate,

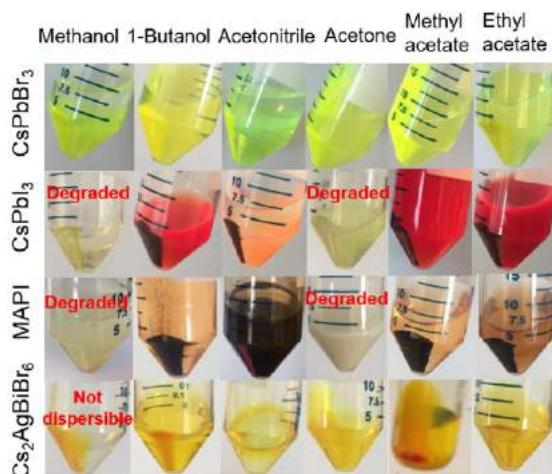


Figure 12. Photographs of centrifuge tubes with CsPbBr_3 , CsPbI_3 , MAPI, and $\text{Cs}_2\text{AgBiBr}_6$ (see **NANOCRYSTALS OF LEAD-FREE PEROVSKITE-INSPIRED MATERIALS** section for synthesis of $\text{Cs}_2\text{AgBiBr}_6$ nanocubes) nanocubes precipitated by centrifugation (8000 rpm (8228g) for 5 min) from crude reaction mixtures with six different polar solvents using equivalent volumes of polar solvent and crude reaction mixture. Nanocube concentrations were about 5–10 mg/mL. Some variation in nanocube concentration occurs because of the differences in reaction yields. Based on measured product yields, the concentrations were 4.3 mg/mL for $\text{Cs}_2\text{AgBiBr}_6$, 9 mg/mL for CsPbI_3 , and 7 mg/mL for CsPbBr_3 and MAPI. Images are adapted from ref 187. Copyright 2020 American Chemical Society. Further permissions related to the material excerpted should be directed to the ACS.

and ethyl acetate. A clear and colorless supernatant indicates that all the nanocubes had been precipitated. There are a few situations where nanocubes are still retained in the supernatant, even with the use of the antisolvent. The expected colors of CsPbBr_3 , CsPbI_3 , MAPI, and $\text{Cs}_2\text{AgBiBr}_6$ nanocubes are yellow-green, dark red, dark brown, and golden-orange, respectively. Precipitation of CsPbI_3 and MAPI nanocubes with methanol and acetone turned the color of the precipitate into pale yellow or milky white. Methanol and acetone are not compatible with CsPbI_3 and MAPI nanocubes, and in general, these two polar solvents should be avoided when purifying iodide-containing nanocubes, including FAPbI_3 . Methanol and acetonitrile are not completely miscible with octadecene, and a liquid–liquid phase separation results that retains some nanocubes in the supernatant, which cannot be isolated. CsPbBr_3 nanocubes are the most stable of these metal-halide perovskite NCs and were found to be compatible with all of the polar antisolvents shown in Figure 12. $\text{Cs}_2\text{AgBiBr}_6$ nanocubes are also relatively stable, although methanol does lead to irreversible aggregation and should be avoided.

In addition to the antisolvent chemistry, the conditions used to precipitate the nanocubes are important. Some of these conditions may seem trivial, like centrifugation time, for example.^{184,185,194,195} For CsPbI_3 nanocubes, 5–10 min of centrifugation at 8000 rpm (8228g) works well. Longer centrifugation times can result in drastically different results, yielding CsPbI_3 nanocubes with very poor dispersibility, low PLQYs, and nanocubes largely transformed to the yellow phase. The precipitate should be separated from the supernatant immediately after centrifugation. Degradation of the sample can continue to occur when the nanocubes remain in the presence of a large volume of polar solvent. The volume

ratio of antisolvent to solvent is important. For example, when CsPbI_3 nanocubes are dispersed in a crude reaction mixture of octadecene or redispersed in hexane at a concentration of about 10 mg/mL, an antisolvent to solvent volume ratio in the range of 1–2 is usually appropriate. This is not quite enough antisolvent to precipitate all of the nanocubes in the sample, but more antisolvent can end up degrading the nanocubes. An antisolvent/solvent ratio of 3, for example, will precipitate nearly all of the nanocubes, but the nanocubes will not be able to be redispersed easily and the PLQYs will be significantly reduced. Anhydrous solvents should be used to minimize degradation induced by water. Although not always necessary, the purification can be carried out in a glovebox under inert conditions. Using that procedure tends to provide nanocubes with longer shelf-life. There is a risk, however, that the sample starts degrading because the extra time spent transferring samples in and out of a glovebox prolongs the exposure of the nanocubes to antisolvent, which can induce such degradation. In general, the purification process should be optimized for each type of nanocube and the synthetic approach that is used. Differences in capping ligand chemistry and concentrations of the crude reaction mixture due to variations in the yields of alternative reactions can all lead to changes in the optimized antisolvent precipitation conditions.

The use of antisolvents to purify metal-halide perovskite nanocubes is essential in some cases. Analytical techniques, like NMR spectroscopy, require samples that are nearly completely free of unbound ligand and other organic impurities. One precipitative washing step is not enough to achieve the necessary level of purity required for these measurements. At least two cycles of precipitative washing are needed.⁸⁴ A second precipitative washing step with antisolvent can degrade iodide-based metal-halide perovskite nanocubes such as CsPbI_3 . To prevent degradation, a small amount of excess ligand (*i.e.*, oleylamine) must be added before the second precipitative wash.¹⁸⁷ Figure 13 shows TEM images and photographs of CsPbI_3 nanocubes after a second precipitation with methyl acetate. Without additional oleylamine, the CsPbI_3

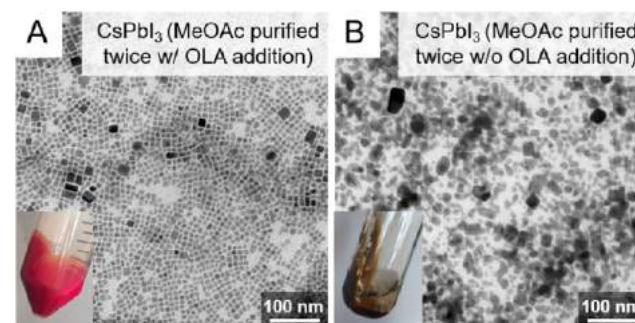


Figure 13. TEM images of CsPbI_3 nanocubes that were precipitated twice with methyl acetate (A) with and (B) without the addition of oleylamine before the second precipitative washing step. The insets show photographs of the products obtained after centrifugation. The nanocubes in (A) were isolated after adding 10 μL of oleylamine to 3 mL of CsPbI_3 nanocubes in hexane at a concentration of 10 mg/mL. Both samples in (A) and (B) were centrifuged at 8000 rpm (8228g) for 3 min after adding 3 mL of methyl acetate (1:1 v/v methyl acetate/hexane). Adapted from ref 187. Copyright 2020 American Chemical Society. Further permissions related to the material excerpted should be directed to the ACS.

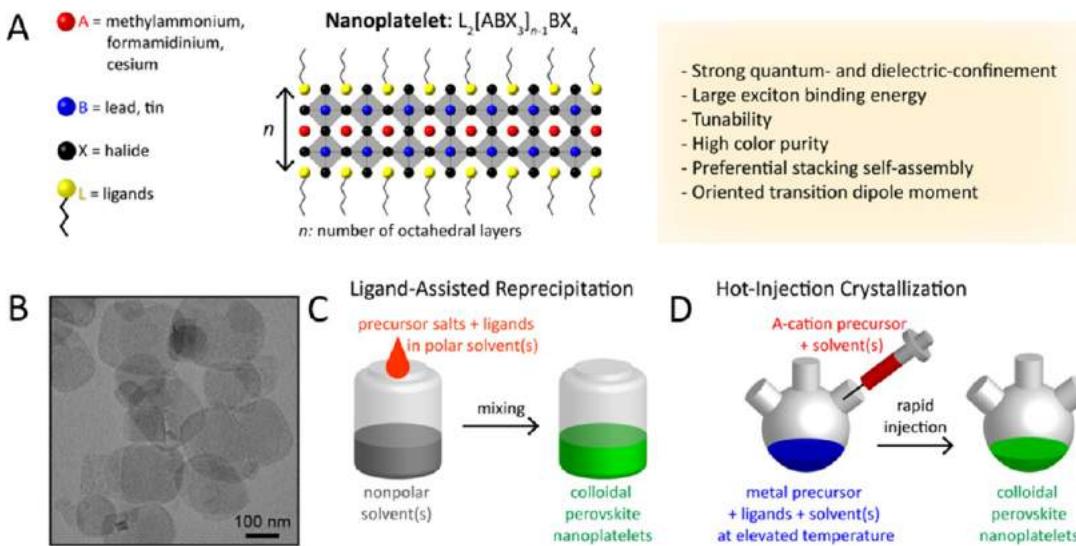


Figure 14. Structure of colloidal perovskite nanoplatelets and synthetic approaches. (A) Perovskite nanoplatelet structure and its distinctive properties. (B) Transmission electron microscopy image of nanoplatelets. Reproduced from ref 209. Copyright 2016 American Chemical Society. (C) Schematic illustration of ligand-assisted reprecipitation method. (D) Schematic illustration of hot-injection crystallization method.

nanocube product ends up with a dull brown color, and the nanocubes are still mostly in the perovskite phase but have lost most of their luminescence and their distinct cubic shape. They do not redisperse in hexane. In contrast, the nanocubes in Figure 13A that were precipitated after an addition of oleylamine (10 μ L) retain their luminescence and cubic shape and disperse readily in hexane. The NMR spectra of these nanocubes also do not show the presence of any free unbound ligand.^{84,145,187} For some nanocubes, however, the addition of oleylamine before a second precipitative wash can lead to degradation, as in the case of $\text{Cs}_2\text{AgBiBr}_6$ nanocubes.¹⁹⁶ Each sample requires optimization of the best purification conditions, but in general, precipitation with polar antisolvents is an effective way to isolate and purify metal-halide perovskite nanocubes.

Summary and Outlook of Perovskite Nanocubes. A wide range of synthetic methods has been reported for mono-disperse CsPbX_3 ($\text{X} = \text{Cl}, \text{Br}$, and I) nanocubes with 80–100% PLQY (for $\text{X} = \text{Br}$ and I) under optimized conditions. Every method has its own advantages and disadvantages. To date, HI and LARP methods have been extensively explored for the synthesis of inorganic perovskite NCs.^{14,53} In particular, HI synthesis is being heavily explored for shape-controlled synthesis of CsPbX_3 NCs using different kinds of precursors and ligands. The role of acid–base equilibria of ligands, precursor types, and the chain length of amines in the shape control of CsPbBr_3 nanocubes have been explored.^{143,145,176,177} In most synthesis methods, long-chain alkylamines have been used as ligands for stabilization of perovskite nanocubes. However, they are problematic for device applications as they block the transport of charge carriers. Therefore, it is important to explore short-chain ligands in future studies for the stabilization of perovskite nanocubes. Although perovskite nanocubes exhibit extremely high PLQYs right after synthesis, their purification leads to a significant reduction in PLQY (~20–40%) due to the removal of ligands from the NC surface. To overcome this problem, bidentate ligands (or chelating ligands) have been proposed for enhanced stability and to retain high PLQY even after purification of nano-

cubes.^{171,172} While CsPbBr_3 nanocubes have been found to be relatively stable over a long time, it is still challenging to obtain strongly luminescent, phase-stable CsPbI_3 nanocubes. Various ligands have been proposed for improving their cubic phase stability; however, the stability is still not comparable to that of CsPbBr_3 nanocubes. On the other hand, despite great progress in the synthesis of inorganic perovskite nanocubes, organic–inorganic hybrid nanocubes have been less explored regarding their shape-controlled synthesis, and future studies could be focused in this direction. In addition, more studies are needed in the future to obtain highly luminescent and stable lead-free perovskite nanocubes (see later sections on lead-free NCs).¹⁹⁷

Nanoplatelets. Origins of Perovskite Nanoplatelets.

Two-dimensional (2D) metal-halide perovskite nanoplatelets trace their origin to the synthesis of Ruddlesden–Popper (R–P) phase-layered perovskite crystals. In the 1990s, it was discovered that substituting the usual small A-site cations (e.g., MA, FA, Cs) for larger organic cations (e.g., butylammonium) could induce the crystallization of layered structures.^{6,127,128,130,198–200} These layered perovskite crystals consist of alternating inorganic layers of lead-halide octahedra and organic cations; the inorganic metal-halide layer primarily determines the optoelectronic properties, and the large organic cation layer electronically isolates the inorganic layers. Because of quantum-confinement effects, layered perovskites exhibit drastically different properties compared to the bulk 3D phase.²⁰¹ Also, layered perovskites showed enhanced stability compared to 3D counterparts due to a negative enthalpy of formation^{49,202,203} as well as the presence of organic spacer layers that protect inorganic layers from external factors such as oxygen and moisture.²⁰⁴

Around 2015, multiple groups reported the synthesis of colloidal perovskite nanoplatelets^{16,18,19,48}—2D perovskite crystals much like their R–P predecessors but dispersed in solution. Colloidal perovskite NPs are generally characterized by the chemical formula of $\text{L}_2[\text{ABX}_3]_{n-1}\text{BX}_4$ (Figure 14A,B) where n indicates the number of inorganic metal-halide octahedral layers in thickness. Thicknesses of NPs are confined to a few unit cells, and NPs can tolerate lateral

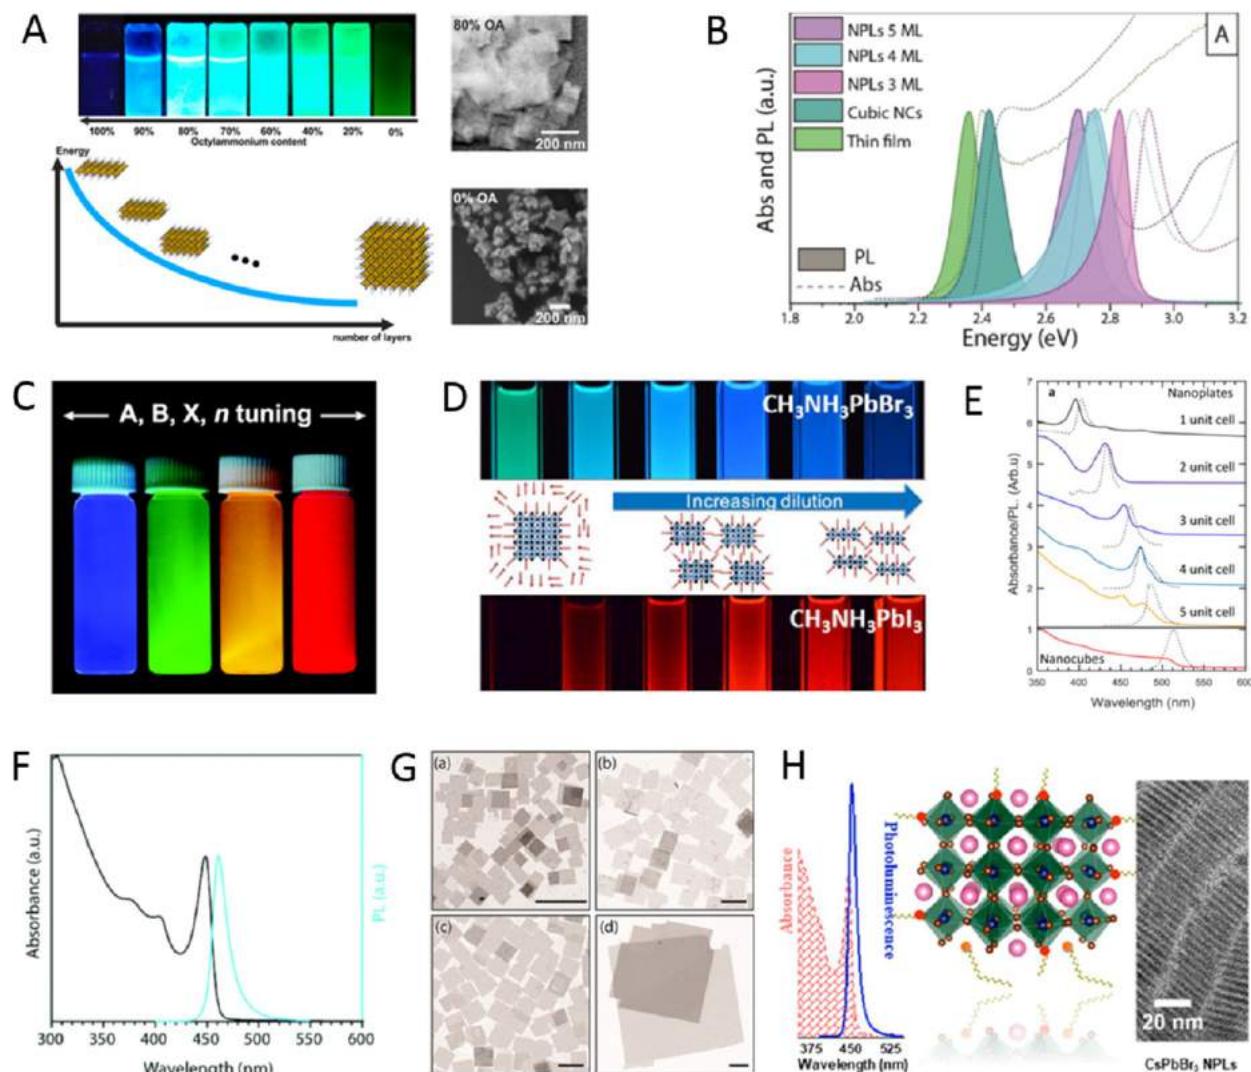


Figure 15. Advancements of colloidal perovskite nanoplatelet synthesis. (A) Synthesis of thickness-controlled MAPbBr₃ nanoplatelets *via* LARP. (B) Synthesis of CsPbBr₃ nanoplatelets *via* LARP. (C) Thickness and compositional tunability of nanoplatelets *via* LARP. (D) Dilution-induced nanoplatelet formation *via* LARP. (E) Thickness-controlled CsPbBr₃ nanoplatelet synthesis *via* HI. (F) $n = 3$ MAPbBr₃ nanoplatelet synthesis *via* HI. (G) Nanoplatelet lateral dimension control through HI synthesis. (H) Synthesis of hexylphosphonate-capped NPs with enhanced stability *via* heat-up approach. Panel A is reproduced from ref 16. Copyright 2015 American Chemical Society. Panel B is reproduced from ref 48. Copyright 2016 American Chemical Society. Panel C is reproduced from ref 209. Copyright 2016 American Chemical Society. Panel D is reproduced from ref 231. Copyright 2016 American Chemical Society. Panel E is reproduced with permission from ref 18. Copyright 2015 American Chemical Society. Panel F is reproduced under a Creative Common [CC-BY 3.0] license with permission from ref 158. Copyright 2016 Royal Society of Chemistry. Panel G is reproduced from ref 217. Copyright 2016 American Chemical Society. Panel H is reproduced under a Creative Common [CC-BY] license from ref 213. Copyright 2020 American Chemical Society.

dimension dispersity as long as thickness homogeneity is ensured.⁴⁷ Surface ligands act as surfactants, entropically stabilizing the 2D crystals in solution, but their role in 2D NC formation is debated.^{205,206} Since layered R-P perovskites can be thought as a crystal of stacked NPs with electronically decoupled inorganic layers, there are many parallels between layered perovskites and perovskite NPs. They seem to be tunable over the same range and composition with identical band gap and optical properties,^{18,47,201,207–209} which implies that previous studies on layered perovskites can also shed light on the properties of colloidal perovskite NPs.

Colloidal perovskite NPs were initially identified as a side product of MAPbBr₃ NC synthesis,¹⁹ but very quickly the ability to precisely control thickness was reported.^{16,18,48,158}

Following these initial works, subsequent efforts focused on developing refined synthetic protocols for NPs with well-controlled thicknesses and improved material properties. For instance, the color of emission can be tuned by varying thickness and composition.^{16,18,48,209–212} Also, reports on the tunability of surface-capping ligands, ranging from short ligands for optimal charge transport behavior to long and functionalized ligands for enhanced stability, have highlighted the possibility of optimizing surface properties of NPs for specific applications.^{212–214} It has also been reported that the lateral dimension of NPs, which may affect electronic transport in NPI optoelectronic devices, can be tuned from tens of nanometers^{18,48,54,158,210,215,216} to several micro-

meters^{47,209,217,218} without loss of quantum confinement in the vertical direction.

Distinctive Properties of Nanoplatelets. 2D nanoplatelets possess distinctive characteristics specific to their 2D shape (Figure 14A). The exciton Bohr radius of lead-halide perovskite materials has been reported to be ~3 nm or larger, depending on composition.^{14,16,47,48,128} It is synthetically challenging to prepare 0D NCs with such small dimensions; however, perovskite NPs as thin as 0.6 nm in thickness^{209,214,219–221} exhibiting strong quantum and dielectric confinement can be easily fabricated. This strong confinement induces excitonic absorption and emission features to be blue-shifted from those of the bulk perovskite phase by up to 0.7 eV,^{47,222} which enables the synthesis of bluer light-emitting NCs. Spatial confinement of excitons in 2D structures also yields large exciton binding energies, reaching up to several hundred meV,^{100,128,130,222} which can facilitate efficient recombination of excitons. Moreover, monodisperse NPs exhibit superior emission color purity due to atomically precise thickness homogeneity. Achieving monodispersity is of great importance for NPs since band gaps of strongly confined NPs show significantly larger shifts when the thickness changes,^{47,209,211} compared to other weakly confined NCs.^{14,223,224} Nonetheless, monodisperse nanoplatelets have been widely demonstrated.^{18,48,60,158,209,210,213,217,221,225,226,54,218}

A 2D structure is ideal for integration into optoelectronic devices. A key feature of 2D NPs is the tendency for the transition dipole moment to preferentially orient within the 2D plane,^{227,228} which is advantageous for optical coupling. Additionally, NPs exhibit face to face stacking^{18,54,224} and preferential face-down assembly on a given substrate.^{209,214,218,229} This tendency—combined with transition dipole anisotropy—leads to preferential emission in the out-of-plane direction.²²⁸ Moreover, large lateral dimensions of NPs^{16,209,217,218} can potentially be utilized to minimize grain boundaries in-plane and lower the percolation threshold for charge transport.²³⁰

Synthesis of Nanoplatelets. Numerous synthetic approaches to perovskite NPs have been developed. In this section, we start with a discussion on the two most widely used techniques—LARP (Figure 14C) and hot-injection crystallization (Figure 14D)—and then introduce other synthetic approaches. The LARP method usually consists of dissolving perovskite NP precursor salts in relatively polar solvent(s) (e.g., DMF and DMSO) and then mixing it with less polar solvent(s) (e.g., toluene, hexane) to induce crystallization at room temperature. In 2015, Sichert *et al.* reported the synthesis of thickness-controlled MAPbBr_3 NPs *via* LARP (Figure 15A).¹⁶ They first dissolved NP precursors (MABr, PbBr_2 , and OABr) in DMF, and NPs were then crystallized upon mixing the solution with excess toluene. Precise tuning of NP thickness was achieved by varying the methylammonium to octylammonium ratio in the precursor solution. Soon after, Akkerman *et al.* reported the synthesis of $n = 3–5$ CsPbBr_3 NPs with modified LARP process where the addition of acetone into the precursor solution mixture induced destabilization of precursor complexes and initiated NP crystallization under ambient conditions (Figure 15B).⁴⁸ They also showed that the band gap of the NPs can be continuously tuned by an anion exchange reaction. Later, Weidman *et al.* published $n = 1$ and $n = 2$ perovskite NPs with wide ranging composition (A = MA/FA/Cs, B = Pb/Sn, X =

Cl/Br/I, ligand = butylammonium/octylammonium) *via* LARP by simply varying the stoichiometric ratios of precursor solutions (Figure 15C).²⁰⁹ Tong *et al.* demonstrated the breakup of large MAPbX_3 NCs synthesized *via* LARP into NPs by diluting the solution, which triggered osmotic swelling by solvent (Figure 15D).²³¹ In addition, Sun *et al.* carried out a systematic study and showed that choosing the right combination of ligand species plays a crucial role in determining the shape of the NCs synthesized *via* LARP.¹⁷⁶

In general, LARP enables facile synthesis of colloidal perovskite NPs with easily tunable composition and ligands. Moreover, LARP can be highly cost-effective as it delivers colloidal perovskite NPs in ambient atmosphere at room temperature. However, thinner NPs synthesized *via* LARP tend to exhibit lower photoluminescence quantum yield,^{16,209,214} and it is difficult to target thicker ($n \geq 3$) dispersions with good thickness control.^{214,232,233} Recent works have focused on refining the synthesis and improving material properties—expanding synthetic capability,^{60,212,220} improving thickness selectivity,^{214,220} modulating surface properties by incorporating different ligand species,^{212,214} boosting photoluminescence quantum yield^{60,211,225} and enhancing material stability.²²⁹ Although significant advancements have been made in the past few years, there is still ample room for further development.

Another widely used synthetic approach is hot-injection crystallization, as described in the previous section. The HI approach is based on the rapid injection of a precursor solution into a solution containing the other precursors, ligands and solvent(s), at elevated temperature. The HI synthesis enables the separation of nucleation and growth of NCs so that it can deliver high-quality NCs.⁵² Also, it does not involve any polar solvent which could potentially be detrimental to colloidal perovskites. Early reports of perovskite NPI synthesis *via* the HI protocol^{18,158} came out a few months after Protesescu *et al.* published the synthesis of CsPbX_3 quantum dots *via* HI.¹⁴ Bekenstein *et al.* found that lowering the temperature of cesium precursor injection into lead-halide precursor solution results in the formation of $n = 1–5$ CsPbBr_3 NPs (Figure 15E).¹⁸ They also demonstrated NPI band gap tuning *via* halide exchange reaction. Around the same time, Vybornyi *et al.* reported the HI synthesis of $n = 3$ MAPbBr_3 NPs (Figure 15F).¹⁵⁸ Along with the previous report from Sichert *et al.* on the synthesis of MAPbBr_3 NPs *via* LARP,¹⁶ those early reports revealed the possibility to synthesize perovskite NPs with control over their thickness. However, it was pointed out that lateral dimensions of perovskite NPs synthesized *via* HI (10–100 nm)^{18,158,210} are generally smaller than those of NPs synthesized *via* LARP (100–1000 nm).^{16,209,214} In response to it, Shamsi *et al.* showed that the lateral dimension of CsPbBr_3 NPs can be increased to several microns by adjusting the ratio of shorter ligands to longer ligands in the synthetic mixture during the HI synthesis (Figure 15G).²¹⁷ Similarly, Zhang *et al.* published the synthesis of micron-sized $n = 2$ FAPbBr_3 NPs.²¹⁸ Furthermore, Pan *et al.* provided deeper insight into HI synthesis by identifying the key factors that control the shape of the NCs in HI synthesis—reaction temperature and choice of ligands.¹⁷⁷

Recent works on NPI synthesis *via* HI have focused on refining the synthesis of NPs accompanied by detailed structural characterizations²¹⁰ and understanding the complex dynamics of the HI reaction.^{145,215} However, the HI synthesis is still highly focused on Cs-based NPs,^{18,145,177,210,215,217} and

there is only a limited number of reports on organic cation-based NPLs.^{158,218} Compared to LARP-synthesized NPLs, HI-synthesized NPLs are generally smaller in lateral dimensions^{18,158,210} and usually capped by longer ligands,^{16,18,209,210} which could undermine electronic transport properties. Since the HI method requires high temperature and inert atmosphere, scalability and cost-effectiveness could be greater barriers to eventual commercialization for HI than for LARP. Historically, HI-synthesized NPLs have shown higher PLQY^{18,48} though the PLQY of LARP-synthesized NPLs has recently become comparable.^{60,211,225,231} Thus, more efforts on further developing HI synthesis of perovskite NPLs are needed.

Apart from LARP and HI, other creative approaches to perovskite NPL synthesis have been demonstrated. Shamsi *et al.* showed that quantum-confined CsPbBr₃ NPLs can be synthesized by mixing of cesium-oleate solution with PbBr₂–ligand complex solution, adding isopropyl alcohol to initiate nucleation and then heating the solution to grow NPLs.²³⁴ A few years later, Shamsi *et al.* slightly modified this heat-up method and demonstrated the synthesis of hexylphosphonate-capped NPLs (Figure 15H).²¹³ They observed that stronger binding of phosphonate ions compared to conventional alkylammonium ions to NPL surface^{177,213} greatly improved the stability of NPLs and suppressed transformation of NPLs into thicker, less-confined structures which can result in the loss of desirable optical properties.^{229,234,235} Huang *et al.* reported the scalable synthesis of $n = 4$ FAPbI₃ NPLs by mixing the FA–ligand complex solution with PbX₂–ligand complex solution in toluene.⁵⁴ This approach was a hybrid of HI and LARP in that it was done under ambient conditions at room temperature but no polar solvent was involved. Another interesting approach is ultrasonication-assisted synthesis: Tong *et al.*³⁰ and Hintermayr *et al.*¹³² reported the synthesis of perovskite NPLs by sonicating the dispersion of perovskite precursors in the presence of coordinating ligands. Lastly, Dou *et al.* demonstrated the direct synthesis of atomically thin monolayer of L₂BX₄ perovskite on the substrate by drop-casting the solution of precursor salts first dissolved in DMF/chlorobenzene cosolvent.¹⁷ Even though this was not a “colloidal nanoplatelet” synthesis, it introduces another promising route to deposit a thin layer of 2D perovskites.

Outstanding Questions and Future Challenges for Nanoplatelets. Although various synthetic techniques have been developed for colloidal perovskite NPLs, a complete understanding of anisotropic perovskite NPL growth is lacking. How can thin 2D structures grow from an isotropic crystal lattice and homogeneous solvent environment? An in-depth study carried out by Riedinger *et al.* on the formation of 2D CdSe NPLs from isotropic materials²⁰⁵ provides some interesting insight. In that paper, the authors started with experimentally verifying that CdSe NPLs can be formed in an isotropic environment in the absence of any molecular mesophases, and then formulated a growth model based on experimental results. General theory of nucleation and growth predicts the growth of a NC to occur through the nucleation of a additional island on one of the facets; when this island reaches a critical size, expansion of the island becomes thermodynamically favorable and leads to the formation of a complete additional layer on that facet. Riedinger *et al.* showed that when specific criteria are met, namely, (1) NC formation occurs through nucleation-limited growth, (2) initial small crystallites can adopt anisotropic 2D shapes due to the random fluctuations in the reaction mixture, and (3) the thickness of

this initial crystallite is smaller than the critical island size—certain combinations of volume, surface, and edge formation energies of NCs in the system can lead to a lower nucleation barrier for narrower facets compared to large planar facets. This lower nucleation barrier results in the faster growth on the narrower facet, which can eventually yield anisotropic 2D NPLs. Their model also predicts higher narrow-facet nucleation barrier for thicker NPLs than thinner NPLs, and it is consistent with the observations by Bekenstein *et al.*¹⁸ and Pan *et al.*¹⁷⁷ that thicker perovskite NPLs were formed at higher reaction temperatures. Although Riedinger *et al.*²⁰⁵ studied the CdSe NPL system, their theoretical model is generalizable to any isotropic materials system, including perovskite NPLs. It should also be noted that, along with reaction temperature, previous reports listed a careful choice of ligands and precise control of perovskite precursor composition and concentration of precursor solution as other key factors in the shape-controlled synthesis of perovskite NPLs.^{145,177,236} We speculate that optimized synthetic conditions in those reports may in fact reflect precisely tuned volume, surface, and edge formation energies of the NC in the system where the formation of anisotropic 2D NPLs is favored. More recently, Burlakov *et al.* proposed a CsPbBr₃ NPL formation mechanism based on the competitive nucleation of an inorganic perovskite layer and an organic ligand layer.²⁰⁶ Being consistent with the discussion above, their work also focused on temperature and interaction energies between constituents as primary factors that determine nucleation kinetics. Through a combination of theoretical and experimental work, they showed that, under certain conditions, narrower facets can favor crystal layer nucleation, while wider facets are more effectively passivated by ligand layer formation, which can lead to anisotropic two-dimensional crystal growth. Their theoretical prediction of preferential formation of thinner NPLs at low reaction temperature was experimentally verified and is also consistent with the observations by Bekenstein *et al.*¹⁸ and Pan *et al.*¹⁷⁷ Still, this picture is far from complete, and we do not yet have a firm grasp on the mechanism of how anisotropic NPLs are formed from isotropic environments.

In addition to open questions regarding nucleation and growth, a detailed understanding of the electronic structure in 2D NPLs is still lacking. Furthermore, it is unclear to what extent perovskite NPLs actually exist as isolated sheets in solution rather than small crystallites of RP phase.²³⁷ Spontaneous stacking^{158,224} and slow precipitation of NPLs²¹⁴ in concentrated solutions have been observed, which may indicate the existence of large RP-phase crystallites with poor colloidal stability. Thus, a systematic study on the behavior of NPLs in colloidal solution is needed for a better solution processability. In addition, efforts are underway to tackle the main drawbacks of perovskite NPLs, namely, improving their low PLQY^{60,225} and enhancing the stability.²²⁹ Additional goals include the synthesis of stable lead-free NPLs,²⁰⁹ doping NPLs to expand their functionality,²³⁸ and integrating NPLs into state-of-the-art optoelectronic devices (see also later sections on these various topics).²¹¹

Nanowires. Semiconductor nanowires are fundamental nanoscale building blocks for nanophotonic platforms such as interconnects, waveguides, and optical cavities. Due to the single-crystallinity and well-controlled interfacial engineering, individual NWs or their assemblies are also ideal model systems for the fundamental study of charge transfer and carrier dynamics at the nanoscale. Metal-halide perovskites

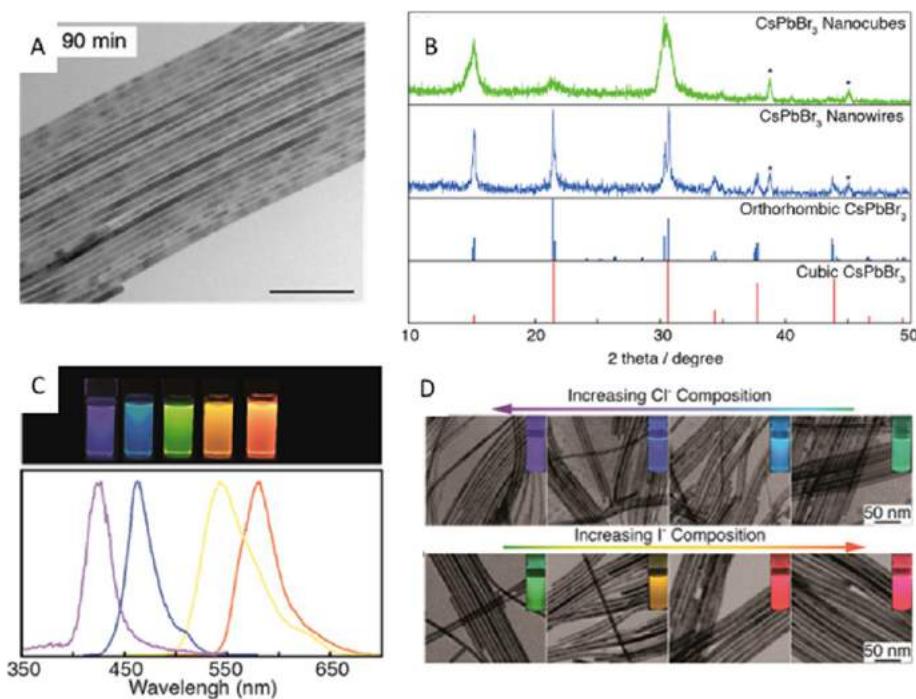


Figure 16. (A) TEM image of colloidally synthesized CsPbBr₃ nanowires. (B) X-ray diffraction spectrum of CsPbBr₃ nanocubes and nanowires. Reproduced from ref 75. Copyright 2015 American Chemical Society. (C) Photoluminescence properties of ultrathin CsPbBr₃ nanowires with different halide compositions. Reproduced from ref 76. Copyright 2016 American Chemical Society. (D) TEM images of anion exchange in CsPbX₃ perovskite nanowires with various halide contents. Reproduced from ref 56. Copyright 2016 American Chemical Society.

have demonstrated a significant level of defect tolerance. The ionic nature of halide perovskites makes them interesting systems to understand charge dynamics in defect tolerant materials compared with covalent inorganic semiconductors. In addition, low-temperature synthesis and facile ion exchange chemistry provide additional possibilities for understanding alloy and heterostructure formation to explore nanoscale properties. In this section, we review the synthetic approaches of inorganic halide perovskite NWs, their self-assembly, anion exchange, phase transition, and their various applications, especially in photonics and thermoelectrics.

Synthesis of Inorganic Perovskite Nanowires. Colloidal Synthesis. One-dimensional (1D) perovskite NWs have attracted attention because of their large morphology anisotropy and quantum mechanical effects associated with the two confined dimensions. Shortly after the successful synthesis of perovskite NCs,¹⁴ halide perovskite NWs were synthesized by controlling the reaction conditions to achieve different aspect ratios, chemical compositions and phases. In the synthesis of NWs, the formation of “isotropic” perovskite NCs typically dominates in the early stage of reaction, which is triggered by the rapid injection of cesium precursor (Cs-oleate) into a hot solution of lead precursor (Pb-halide) with the proper choice of organic ligands such as oleic acid, oleylamine, and octylamine.^{74,75} In 2015, Zhang *et al.*⁷⁵ reported the solution-phase colloidal synthesis of CsPbBr₃ perovskite NWs that exhibit orthorhombic crystal structure (Figure 16A,B). Later, it was found that NWs evolve through a linear growth, their aspect ratio quickly increases over time and the NW lengths up to 5 μ m are easily reached.²³⁹ Inspired by this approach, Tong *et al.*²² reported the synthesis of CsPbBr₃ NWs by ultrasonication of precursor powders and ligands. They found that, different from a linear growth mechanism in

the hot inject synthesis, the initially formed nanocubes gradually transform into NWs through the oriented attachment mechanism. These methods seem to work quite well for CsPbBr₃ NWs. However, the growth of CsPbI₃ NWs was found to be characterized by much faster kinetics and less controllable size and phase: although the cubic phase of CsPbI₃ can be stabilized at high temperature (above 360 °C), especially at the nanoscale, it spontaneously transforms into the room-temperature stable orthorhombic phase characterized by 1D chains of edge-sharing octahedra. A recent study suggested that, at the initial growth stage of orthorhombic CsPbI₃ NWs, the cubic phase CsPbI₃ nanocubes show lattice distortion induced by the polar solvent molecules, which triggers hierarchical self-assembly of CsPbI₃ nanocubes into single-crystalline NWs through an orientated attachment process.¹⁸⁶ This distinct crystal structure of the CsPbI₃ NWs leads to their distinctive optical behaviors at room temperature. Unlike the narrow and strong excitonic emission from CsPbBr₃ NWs, the CsPbI₃ NWs show a broad and low-energy emission that is attributed to the indirect band gap transition of the orthorhombic phase.²⁴⁰

Ultrathin perovskite NWs with a diameter less than the exciton Bohr radius down to atomic level (<3 nm) are additionally interesting due to their potential quantum-confinement effects.⁷⁶ Zhang *et al.* developed a method to improve both purity and yields of ultrathin NWs from colloidal synthesis.⁷⁶ The ultrathin CsPbBr₃ NWs showed a strong photoluminescence at ~465 nm, which is significantly blue-shifted compared to the emission wavelength for bulk CsPbBr₃ (~530 nm) (Figure 16C,D). A surface treatment with PbBr₂ precursor led to an increase in both PLQY and stability of the NWs by retarding the ripening process. Similarly Imran *et al.* developed a method to grow CsPbBr₃ NWs with a width that

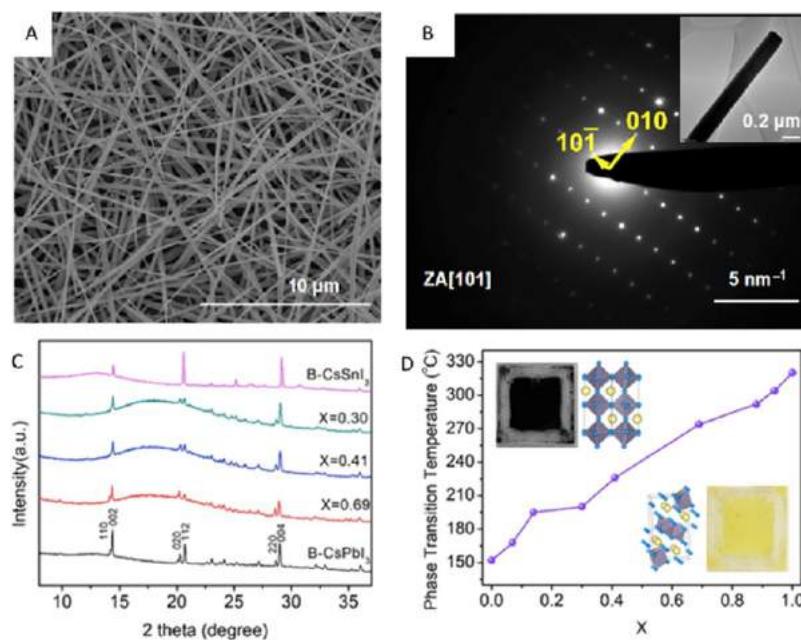


Figure 17. (A) SEM images of CsPbI_3 nanowires grown on a glass substrate from solvent evaporation method and (B) Selected area electron diffraction pattern of a single nanowire to confirm the single-crystalline orthorhombic CsPbI_3 phase. Reproduced with permission from ref 240. Copyright 2017 Springer Nature. (C) X-ray diffraction patterns of black phase $\text{CsPb}_x\text{Sn}_{1-x}\text{I}_3$ nanowire mesh. (D) Phase transition temperature of $\text{CsPb}_x\text{Sn}_{1-x}\text{I}_3$ nanowires as a function of Pb content in alloy composition. Reproduced with permission from ref 243. Copyright 2018 American Chemical Society.

could be tuned down to the quantum-confinement regime (3.4 ± 0.5 nm), using short carboxylic acids and long alkylamines as the growth medium.⁷⁴ From their study, the increased concentration of short carboxylic acid over the long ligand led to a reduction in the NW width.

To achieve the composition tunability in colloidally synthesized halide perovskites, the facile anion exchange process has been applied to perovskites with different morphologies and is discussed extensively in the **Composition Control by Ion Exchange and Suppression of Exchange** section of this review.^{55,57} Halide anion exchange chemistry in CsPbX_3 NWs represents a powerful strategy for attaining band gap tunability across the blue to near-IR wavelength region.⁵⁶ Post-synthetic chemical transformations have been used in halide perovskites to obtain broad compositional tunability. CsPbBr_3 NWs were used as the starting materials, and the CsPbX_3 alloy NWs with a wide range of halide compositions can be achieved through anion-exchange reactions using organic or inorganic halide precursors. The anion-exchange reaction in perovskite NCs typically happens at the nanocrystal–solvent interface and at room temperature. The PL of CsPbX_3 NWs is easily tunable across the entire visible range by varying the halide composition in a similar way to CsPbX_3 nanocubes.

Solvent-Evaporation-Induced Nanowire Growth. In addition to the inorganic perovskite NW synthesis using colloidal methods, single-crystalline micrometer-sized perovskite NWs can be synthesized using the surfactant-free, substrate-assisted dissolution–recrystallization growth method.^{240–242} Here, the polycrystalline thin film of PbX_2 acts as the seed to initiate the perovskite NW growth by immersing it into a diluted cesium-halide precursor solution. The lead precursor slowly dissolves and recrystallizes with the surrounding cesium precursor to form one-dimensional perovskite single crystals (Figure 17A,B). The appropriate balance between the choice of high halide salt solubility and low perovskite solubility is the key to

achieve effective transformation of perovskite NWs from the seeding layer. This method has been applied to perovskites with different phases and compositions.²⁴² For example, and as already stated earlier, the CsPbI_3 system can adopt either the non-perovskite yellow phase (double chain orthorhombic structure) or the black perovskite phase through the rapid thermal quenching process.²⁴⁰ The synthesis of single-crystalline perovskite alloys with mixed “B”-site cation has been challenging due to the thermodynamically favorable phase separation in solution. Lei *et al.* successfully synthesized single-crystalline $\text{CsPb}_x\text{Sn}_{1-x}\text{I}_3$ NWs (Figure 17C) with the substrate-based solvent evaporation method.²⁴³ In particular, the yellow phase and the black phase $\text{CsPb}_x\text{Sn}_{1-x}\text{I}_3$ NWs can easily be interconverted by carefully tuning of the quenching temperature. The transition temperature increases from 152 to 320 °C as the Pb concentration increases in $\text{CsPb}_x\text{Sn}_{1-x}\text{I}_3$ NWs (Figure 17D). The electrical conductivity of direct band gap black phase $\text{CsPb}_x\text{Sn}_{1-x}\text{I}_3$ is 3–4 orders of magnitude higher than that of the yellow phase $\text{CsPb}_x\text{Sn}_{1-x}\text{I}_3$ NWs. In addition to the mixed “B”-site cation perovskites, mixed alloyed NWs can also be prepared by adjusting the ratios of halides (I, Br, Cl) or A-site cations (MA, FA, Cs).^{244,245}

Vapor-Phase Transport and Growth. For hybrid organic–inorganic perovskites, direct vapor-phase growth is challenging due to the decomposition of the organic cation from the perovskite before vaporization. However, this is not a problem for all-inorganic CsPbX_3 perovskite systems and they can be easily obtained at ~ 450 °C. By precise control of reactant transport and epitaxial substrate selection (mica, sapphire *etc.*), the perovskite NWs can achieve controlled alignment and orientation with tunable compositions.^{246–249} For example, the CsPbBr_3 NWs can be grown such that they are horizontally aligned on the mica substrate, and the size distribution spans from less than 200 nm to a few microns (Figure 18).²⁴⁹ With the same synthetic approach, the growth of perovskite NWs

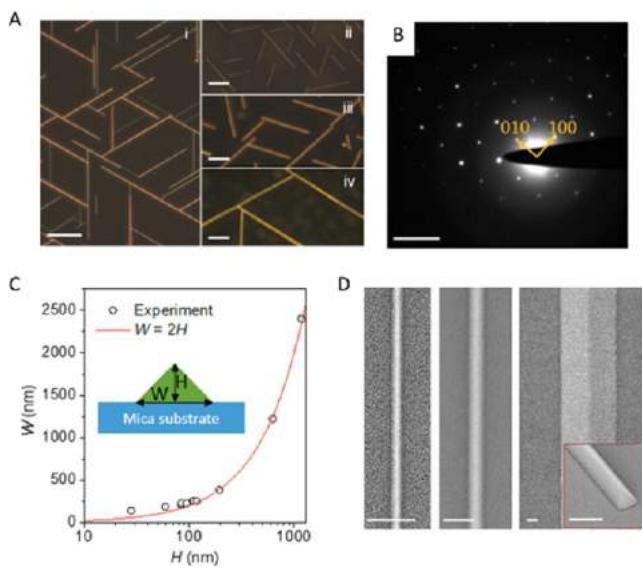


Figure 18. (A) Optical dark-field images of CsPbBr₃ nanowires grown on the mica substrate from chemical vapor transport method and (B) selected area electron diffraction patterns from CsPbBr₃ nanowires with a high single crystallinity. (C) Mapping of nanowire geometry on the mica substrate for the width and height. (D) SEM images of individual CsPbBr₃ nanowire with different lateral widths from left to right (scale bar, 500 nm). Reproduced from ref 249. Copyright 2018 American Chemical Society

can be controlled in the in-plane direction by the graphoepitaxial effect on sapphire substrate.²⁵⁰ A comparative study of epitaxial and graphoepitaxial growth has been conducted with CsPbBr₃ NWs.²⁵¹ The graphoepitaxial growth of CsPbBr₃ NWs results in the bidirectional growth and horizontal alignment on a faceted sapphire substrate. The CsPbBr₃ NWs grown epitaxially on the flat sapphire plane show six isoperiodic directions. Such facile synthesis and controllability of large-scale nanowire networks could potentially facilitate their integration in electronic devices. These single crystals are highly photoluminescent with tunable emission wavelengths, making it possible to observe phase transitions and physical property evolution through an optical approach. Vapor-phase grown single-crystal perovskites can provide an excellent platform for fundamental understanding of the lattice dynamics and transport properties, considering their high crystalline quality, low defect density, and controllable morphologies.

Anion Exchange and Phase Transition in Perovskite Nanowires. Compared to many of traditional covalent semiconductors, the soft nature of the crystal lattice and the weak ionic bonding enable higher reconfigurability in halide perovskites. Consequently, a significant ionic migration is expected in the halide perovskite lattice, which is considered as a possible origin for anomalous hysteresis, light-induced phase segregation and photoinstability. A fundamental understanding of the ionic behavior in halide perovskites has been primarily based on conventional charge transport studies, which only

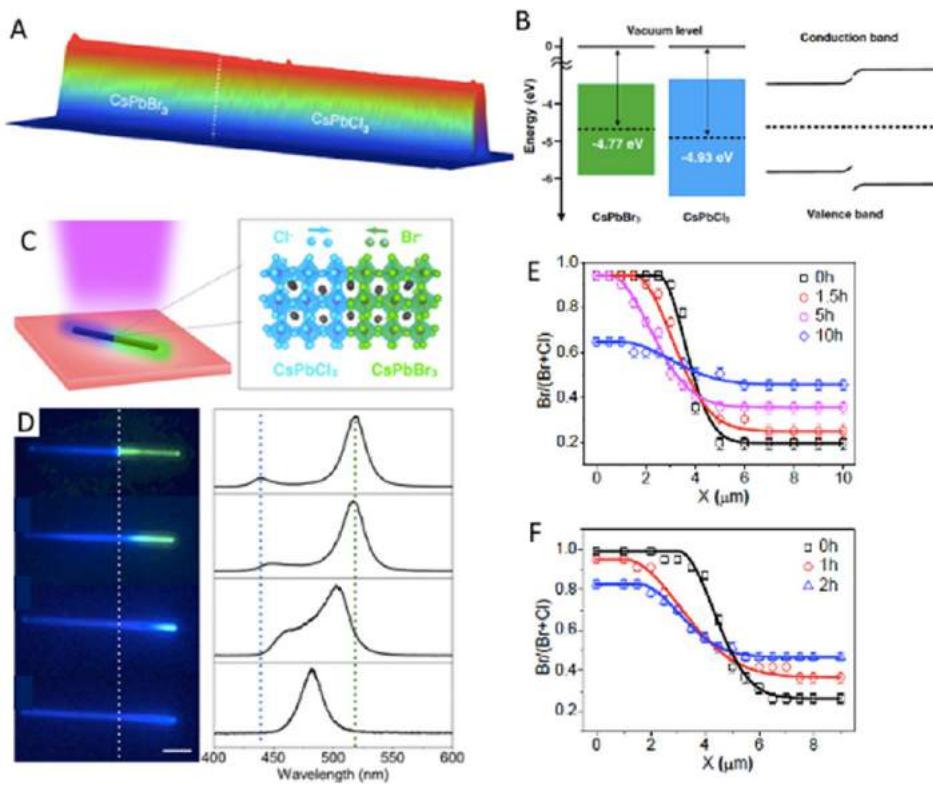


Figure 19. (A) Three-dimensional atomic force microscopy image of CsPbCl₃–CsPbBr₃ nanowire heterostructure. (B) Corresponding electronic work functions determined by Kelvin probe force microscopy and the electronic band alignment of CsPbBr₃–CsPbCl₃ nanowire. Reproduced with permission from ref 252. Copyright 2017 National Academy of Sciences of the United States of America. (C) Schematic illustration of perovskite nanowire heterostructure of CsPbBr₃–CsPbCl₃ nanowire. (D) PL evolution of nanowire heterostructure as a function of anion interdiffusion time due to the heat treatment. (E,F) Halide concentration profiles of perovskite nanowire heterostructure that measured from confocal PL. Reproduced with permission from ref 255. Copyright 2018 National Academy of Sciences of the United States of America.

revealed long-range diffusion on average at the macroscopic level. By combining anion exchange chemistry with nano-fabrication techniques, single-crystalline halide perovskite NW heterostructures have been synthesized.^{252,253} The spatially resolved multicolor CsPbX_3 ($X = \text{I}, \text{Br}, \text{Cl}$ or alloy of two halides) NWs show a sharp electronic interface of the heterojunctions, which enables a quantitative study of ion interdiffusion and migration dynamics. Unlike the single-crystalline nanostructured perovskite, ionic migrations/diffusions across the grain boundary in polycrystalline thin film are usually faster than inside the lattice.^{15,254} Thus, the high ionic conductivity from polycrystalline thin films may not truly represents the intrinsic properties.

Heterostructures of single-crystalline CsPbX_3 perovskite NWs with two different halide species (CsPbBr_3 – CsPbCl_3) were used as a model system to understand ionic diffusion in halide perovskites (Figure 19A,B).²⁵⁵ The heterostructures exhibit two-color PL emission with a sharp interface. The sharp interface, with one-dimensional control, makes these highly crystalline heterojunctions ideal systems to study the intrinsic halide anion interdiffusion because of the well-defined morphology and absence of grain boundary. The changes in surface potential between two components show distinctive electronic properties across the heterostructure NW. The single-crystalline CsPbX_3 NWs that were grown on epitaxial substrates were also used to study the kinetics of ion exchange.²⁵⁶ For example, CsPbCl_3 , MAPbBr_3 , or MAPbI_3 microplates were grown from the solution-based approaches and transferred on top of aligned CsPbBr_3 NWs on fluorinated-mica substrates. The corresponding solid-state anion interdiffusion could be studied using time-dependent confocal PL microscopy (Figure 19C–F). The temperature-dependent measurements revealed the interdiffusion coefficient of chloride to bromide, along with an activation energy of 0.44 eV.

The variation in electronic band gaps can be exploited to monitor not only the ion migration, but also solid-state phase transition dynamics. *In situ* characterization of the phase transition dynamics (from perovskite phase [α - or γ -phase] to non-perovskite phase [β -phase]) in CsPbIBr_2 NWs has been probed in microscopic channels with high spatial resolution, providing an opportunity to determine the underlying relationships between physical crystal structures and their thermal/electronic properties.²⁵⁷ To observe the thermally induced phase transition dynamics, cathodoluminescence (CL) (luminescence induced by an electron beam) and secondary electron images were simultaneously collected at high frame rates with low electron dose, using a customized scanning electron microscope. The non-perovskite phase of CsPbIBr_2 shows a larger, indirect band gap, with a low PL emission intensity, and the perovskite phase of CsPbIBr_2 shows instead a smaller, direct band gap with a bright PL emission. The difference in emission wavelength yields distinctive contrast in CL imaging, which allows one to track the phase transition dynamics. The phase propagation rates along the NWs were measured by increasing the temperature from 163 to 182 °C. An activation energy of 210 ± 60 kJ/mol was extracted, pointing toward an Arrhenius-like behavior. The microscopic mechanism of phase propagation dynamics was studied from the molecular dynamics simulations, revealing the structurally disordered, liquid-like interface as the origin of the increase in entropy for interphase boundary propagation.

Additionally, p–n junction formation can be fabricated with the single-crystalline CsSnI_3 NWs by utilizing a localized, thermally driven phase transition.²⁵⁸ CsSnI_3 undergoes a thermally driven phase transition from the double-chain non-perovskite yellow phase to the orthorhombic black perovskite phase at ~ 150 °C, and the formation energies of cation and anion vacancies in these two phases are significantly different, which leads to n- and p-type electrical characteristics for yellow and black phases. The carrier mobility of black phase CsSnI_3 is $\sim 400 \text{ cm}^2 \text{ V}^{-1} \text{ s}^{-1}$, while that of the yellow phase CsPbSnI_3 is 2 orders of magnitude lower ($\sim 0.9 \text{ cm}^2 \text{ V}^{-1} \text{ s}^{-1}$). Also, using the CL microscopy technique, the interface formation and propagation between two phases could be directly monitored.

Perovskite NWs have received considerable attention in lasing (see Lasers section) and optoelectronic devices. Therefore, exploring the thermal transport properties of single-crystalline solids is crucial for developing micro-electronic devices. One of the distinctive characteristics of halide perovskite NWs is the coupling between inionic crystal lattice and the confining one dimensional geometry. Combined with the heavy elements (Pb, Sn) in the halide perovskite structure, thermal conductivity in halide perovskites can be greatly reduced, which may significantly boost the thermo-electric performance (Figure 20),²⁵⁹ especially when the

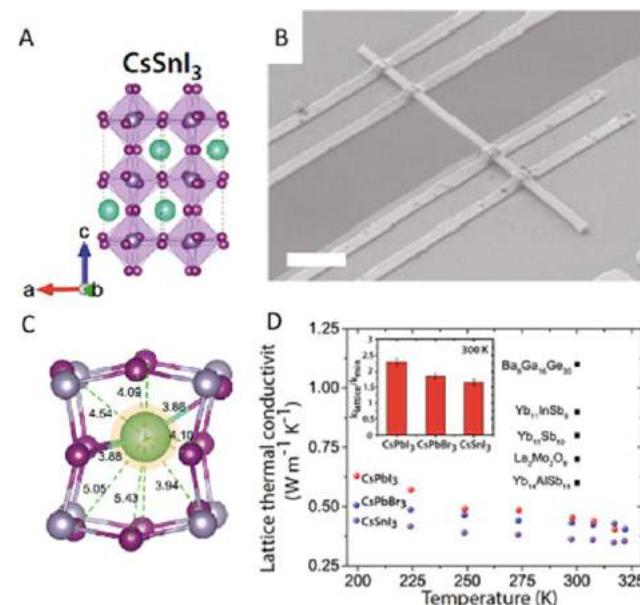


Figure 20. (A) Crystal structures of CsSnI_3 perovskite. (B) SEM images of single nanowire on microisland device. (C) Inhomogeneous bonding structure of atomic cluster rattling mechanism in CsSnI_3 . (D) Comparison of thermal conductivity in perovskites and other crystals. Reproduced with permission from ref 259. Copyright 2017 National Academy of Sciences of the United States of America.

diameter of NW is smaller than the length of the phonon mean free path. The thermal conductivity has been shown to be ultralow ($\sim 0.5 \text{ W m}^{-1} \text{ K}^{-1}$ at room temperature) in CsPbI_3 , CsPbBr_3 , and CsSnI_3 perovskite NWs. Interestingly, these NWs exhibit crystal-like thermal conductivity in which the lattice thermal conductivity initially increases and then decreases as the temperature increases. The ultralow thermal conductivity of inorganic perovskite NWs was attributed to the cluster rattling mechanism based on phonon–phonon

scattering measurements.²⁵⁹ Compared to the inorganic perovskites, a large reduction of thermal conductivity (0.22 W m⁻¹ K⁻¹) was observed in the organic–inorganic hybrid MAPbBr₃ NWs.²⁶⁰ In addition, temperature-dependent measurements revealed the dynamic disorder of the organic cations in MAPbBr₃ NWs, which affects the thermal conductivity at low temperature.²⁶⁰ On the other hand, the effects of phonon group velocity and the high Umklapp scattering rate are dominant in MAPbI₃ NWs at high temperatures.²⁶⁰

Synthesis of Organic–Inorganic Hybrid Perovskite Nanowires. Unlike in the case of colloidal inorganic CsPbX₃ perovskite NWs, only limited research progress has been made regarding the controlled synthesis and applications of colloidal OIH perovskite nanowires. Most of the studies on OIH perovskite NWs have been focused on growing them on substrates for optoelectronic and photovoltaic applications.^{261–266} In 2014, Horváth *et al.*²⁶⁶ reported the fabrication of methylammonium lead iodide (CH₃NH₃PbI₃; MAPI) perovskite NWs by a slip-coating method. This method relies on drying a saturated solution of MAPI dissolved in DMF in a confined volume between two glass plates. However, the NWs were rather thick, with a diameter in the range of 50 and 400 nm. In a subsequent work, Im *et al.* demonstrated the fabrication of dense MAPI NWs films for solar cell applications.²⁶⁷ The NWs were grown on a TiO₂ layer substrate by two-step spin-coating using a DMF–isopropyl alcohol (IPA) solution of MAPI precursor. It was found that the amount of DMF and the concentration of MAPI in the precursor solution is critical for NW formation, and the thickness and length of the NWs can be controlled by varying the amount of DMF. In a follow-up work, the same group carried out a detailed analysis of the intermediate structures during the crystallization of NWs, and they found that the intermediate phase MAI–PbI₂–DMF acts as a structure-directing agent.²⁶⁸ Interestingly, it was found that the treatment of perovskite thin films with a mixture of DMF/IPA could also lead to the formation of perovskite NWs through dissolution and recrystallization.²⁶¹ In addition, predesigned templates could also be used to guide the crystallization of perovskite into NWs. For instance, Spina *et al.*²⁶⁹ demonstrated the fabrication of MAPI NW arrays in open nanofluidic channels, by which it was possible to control the thickness, length, cross-sectional shape, and orientation of the NWs. Similarly, anodized aluminum oxide templates were used for the fabrication of uniform perovskite (CH₃NH₃PbI₃ and CH₃NH₃PbBr₃) NW arrays with a controlled diameter (50–200 nm) on ITO substrates.²⁷⁰ The NWs prepared by these template approaches appear to have rather rough surfaces. Similar to the case of inorganic perovskite NWs, it has been shown that high-quality HOI perovskite NWs with smooth surfaces and a rectangular cross section can be prepared on silicon substrates by vapor-phase synthesis.²⁷¹ This is a two-step fabrication process. First, chemical vapor disposition of PbX₂ precursor powders at high temperature leads to the formation of PbX₂ NWs, which then convert into MAPbX₃ by chemical evaporation of MAX in the same reaction chamber.²⁷¹ These OIH perovskite NWs exhibit room-temperature lasing characteristics upon optical pumping.

A few attempts have been made toward the solution-phase synthesis of high-quality OIH perovskite NWs by the LARP approach.^{272–274} This approach was initially applied to obtain brightly luminescent small NCs. However, this reaction

generally yields a side product consisting of larger nanocubes and NWs in the sediment. Zhang *et al.*²⁷² showed that this LARP reaction produces either high-quality larger MAPbBr nanocubes or NWs upon stirring the reaction mixture for longer times (24 h). The morphology is controllable from nanocubes to NWs by adjusting the amount of ligand solution (octylamine). Debroye *et al.*²⁷³ further extended this approach to MAPI NWs. They used both oleylamine (OLA) and oleic acid (OA) as ligands and found that the length of the NWs increases with increasing the amount of OLA in the reaction medium with a fixed amount of OA. This was attributed to the differences in surface binding kinetic of two different ligands to specific crystal facets.²⁷³ The NWs were found to be single-crystalline and they exhibit longer PL lifetimes. However, the exact mechanism behind the morphology control is still unexplored.

Synthesis of MHP NCs on Substrates (*In Situ* Synthesis). Despite the great success of HT and LARP methods in the shape-controlled synthesis of high-quality perovskite NCs, they also suffer from their fragile surface chemistry and instability. In particular, preserving their superior optical properties when processing them into thin films or embedding them into solid matrix has been challenging. To overcome such problems, an *in situ* synthesis strategy (*i.e.*, synthesis on a substrate) has been employed to colloidal synthesis since the 1990s.²⁷⁵ Because of the high formation enthalpy of II–VI semiconductors, the *in situ* fabrication of conventional quantum dots usually requires high reaction temperature, which affects their optical properties with large full width at half-maximum (fwhm) and low PLQY.²⁷⁶ On the other hand, perovskites are ionic semiconductors with low formation enthalpy and are defect-tolerant.^{98,277} These two features make the *in situ* synthesis strategy well-suited for fabrication of high-quality MHP NC-based nanocomposites for color conversion applications²⁷⁸ or MHP NC thin films for electroluminescence devices.²²⁴ Through this approach, MHP NCs can be directly synthesized in a hard matrix such as porous aluminum oxides,²⁷⁹ glasses,^{280–282} molecular sieves,²⁸³ or in a soft polymeric matrix.²⁷⁸ It is worth mentioning that the *in situ* fabricated perovskite NC–polymer composite films have been successfully applied in TCL TV products.²⁸⁴

Considering the unique advantages of this approach, there has been a growing interest in *in situ* synthesis of perovskite NCs directly on a substrate or in a matrix. As illustrated in Figure 21, mainly four types of substrates have been reported for *in situ* synthesis of perovskite NC composites: (1) glass matrix (for NC-doped glasses, only suitable for inorganic perovskite NCs due to high reaction temperature), (2) molecular sieves, (3) polymer matrix, (4) glass surface (for obtaining perovskite NC films by *in situ* LARP approach). The first three substrates offer a constrained space for perovskites to crystallize it, which can be called nanoconfined crystallization. However, unlike solution-phase colloidal synthesis, the shape of the NCs cannot be controlled with these *in situ* synthesis strategies.

As shown in Figure 22a, Zhong and co-workers developed the *in situ* fabrication strategy to obtain flexible and free-standing perovskite NC–polymer composite films.²⁷⁸ The fabrication process exploited the solubility difference between polymer and perovskites, enabling the formation of small size NCs in the polymeric matrix. The as-prepared composite films exhibit improved stability and enhanced PL emission, along

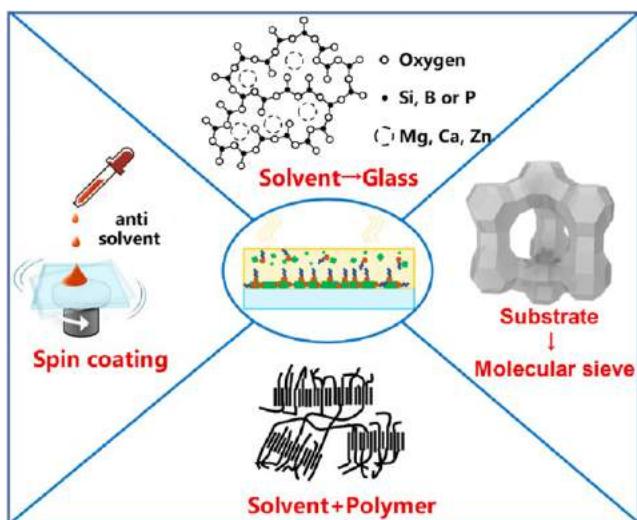


Figure 21. Schematic illustration of four types substrates used in *in situ* synthesis for perovskite NC composites.

with excellent mechanical and also piezoelectric properties. Furthermore, the authors demonstrated the early liquid crystal display backlights based on perovskites. Meanwhile, Wang *et al.*²⁸⁵ demonstrated a swelling–deswelling microencapsulation strategy for the fabrication of MAPbBr_3 –polymer composites (Figure 22b). In this approach, the introduction of the perovskite precursor solution into the polymer matrix leads to solvent-induced polymer swelling, which then deswells after the removal of the solvent by annealing. In 2018, Zhong’s group demonstrated the *in situ* synthesis of highly luminescent FAPbBr_3 NC films on ITO-coated glass substrates.²²⁴ Their approach relies on the crystallization of smooth NC film directly on a substrate by LARP (Figure 22c). The prepared films exhibited bright luminescence with a PLQY up to 78%. They demonstrated that the green LEDs made out of these films exhibit external quantum efficiency up to 16.3%. Figure 22d illustrates a synthesis route for the preparation of a perovskite NC–glass composite. This method relies on heating (at 1300 °C) and then quenching a mixture of perovskite precursors (PbO , CsCO_3 , KX , and so on) and glass melt (SiO_2 , B_2O_3 , and P_2O_5 , and so on) to obtain a transparent glass substrate embedded with perovskite precursor.²⁸² The precursors in glass matrix can be transformed into perovskite NCs either by laser irradiation or by thermal annealing. By precisely controlling the laser focal point, one can draw reversible fine patterns of perovskite NCs in the glass matrix (inset of Figure 22d). On the other hand, a uniformly doped luminescent glass substrate can be produced by thermal annealing at 400–600 °C (Figure 22d, right side).²⁸¹ A similar strategy could be applied to obtain perovskite NC-doped phosphors using a mixture of perovskite precursors and a molecular sieve, as shown in Figure 22e.²⁸³ In this approach, highly luminescent perovskite NC-doped phosphor with ultrahigh stability can be achieved by washing away the unbound perovskite NCs.

Composition Control by Ion Exchange and Suppression of Exchange. *Anion Exchange. Halide Exchange and Mixed-Halide NCs.* The band gap and therefore the color of the emission in lead-halide perovskite NCs is mainly defined by halide atom, with CsPbCl_3 NCs emitting in the blue, CsPbBr_3 in the green, and CsPbI_3 in the red visible spectral range. Mixing of the halide composition ($\text{Br}_x\text{Cl}_{1-x}$; $\text{Br}_x\text{I}_{1-x}$)

provides the possibility of fine-tuning the emission wavelength across the visible range. Mixed-halide composition was already reported in the early report on colloidal lead-halide perovskite NC by Protesescu *et al.*¹⁴ through direct synthesis. This work was quickly followed up by reports on post-synthesis exchange of the halide anions by Kovalenko’s and Manna’s groups. Nedelcu *et al.*⁵⁵ and Akkerman *et al.*⁵⁷ showed that fast anion exchange between Cl and Br, and Br and I could be reversibly achieved by providing the halide sources to the already synthesized NCs in dry octadecene. This reaction worked for all tested halide sources, from organometallic Grignard reagents (MeMgX) to oleylammonium halides (OLAX) and simple PbX_2 salts, without affecting the cationic sublattice and by maintaining the cubic crystals structure and the size of the parent NCs. In this way, the anion exchange provided a synthesis strategy for mixed-halide CsPbBr/I and CsPb Br/Cl NCs with good size monodispersity, which translated to improved optical properties such as emission line width and intensity. Gradual halide exchange from Cl to I or *vice versa* was not achieved; in these attempts, the NCs were either shattered⁵⁷ or quickly converted to single halide crystals,⁵⁵ which was attributed to the large difference between the ionic radii of Cl and I atoms. Furthermore, anion exchange was also observed without the use of additional halide sources by direct mixing of CsPbBr_3 NCs with CsPbI_3 or CsPbBr_3 NCs in colloidal solutions. Here, the NCs can serve as halide sources, and fast shuttling of halide anions between NCs occurs until a homogeneous distribution within the sample is reached.

Toward the fabrication of perovskite NCs with tunable emission for lighting application, the anion exchange process was integrated in a microfluidic reactor system for the synthesis of CsPbX/Y NCs with mixed-halide composition by Kang *et al.*²⁸⁶ Here, the CsPbBr_3 NCs were fabricated in a first microreactor stage, and then the anion exchange with I and Cl occurred in a second reactor, where the respective halide precursors were added to the flow of the CsPbBr_3 NCs that were formed in the first reactor. *In situ* control of the flow parameters of the precursors and monitoring of the PL emission enabled fine control of NC size and composition.

Anion exchange reactions also allowed to extend the range of Pb-free double perovskite NC materials. Creutz *et al.*¹⁸³ fabricated elpasolite $\text{Cs}_2\text{AgBiX}_6$ (X = Cl, Br) NCs and then used the anion exchange with I to obtain $\text{Cs}_2\text{AgBiI}_6$ NCs, which could not be prepared by a direct synthesis route. This Pb-free material is a strong photoabsorber across the visible range and is therefore attractive for photovoltaic applications.

In Situ Monitoring of Anion Exchange. The bright photoluminescence of the mixed cesium lead halides enabled *in situ* monitoring of the anion exchange dynamics in the NCl samples. Koscher *et al.* measured the PL spectra over time during the anion exchange reaction from CsPbBr_3 to CsPbCl_3 and CsPbI_3 NCs in solution ensuring fast injection by a stopped-flow injector.²⁸⁷ The reaction kinetics were analyzed *via* the band gap and PL line width change during the chlorine and iodine exchange. These experiments allowed them to draw a kinetic model for the exchange reaction process, in which distinctly different behaviors were observed for the two reactions. The red shift of the band gap in the exchange from CsPbBr_3 to CsPbI_3 followed a monoexponential trend, and this rapid initial alloying was attributed to a surface-limited process. The more complex kinetics for the exchange with chlorine, which manifested with different time intervals with nearly constant band gap change, could be assigned to a

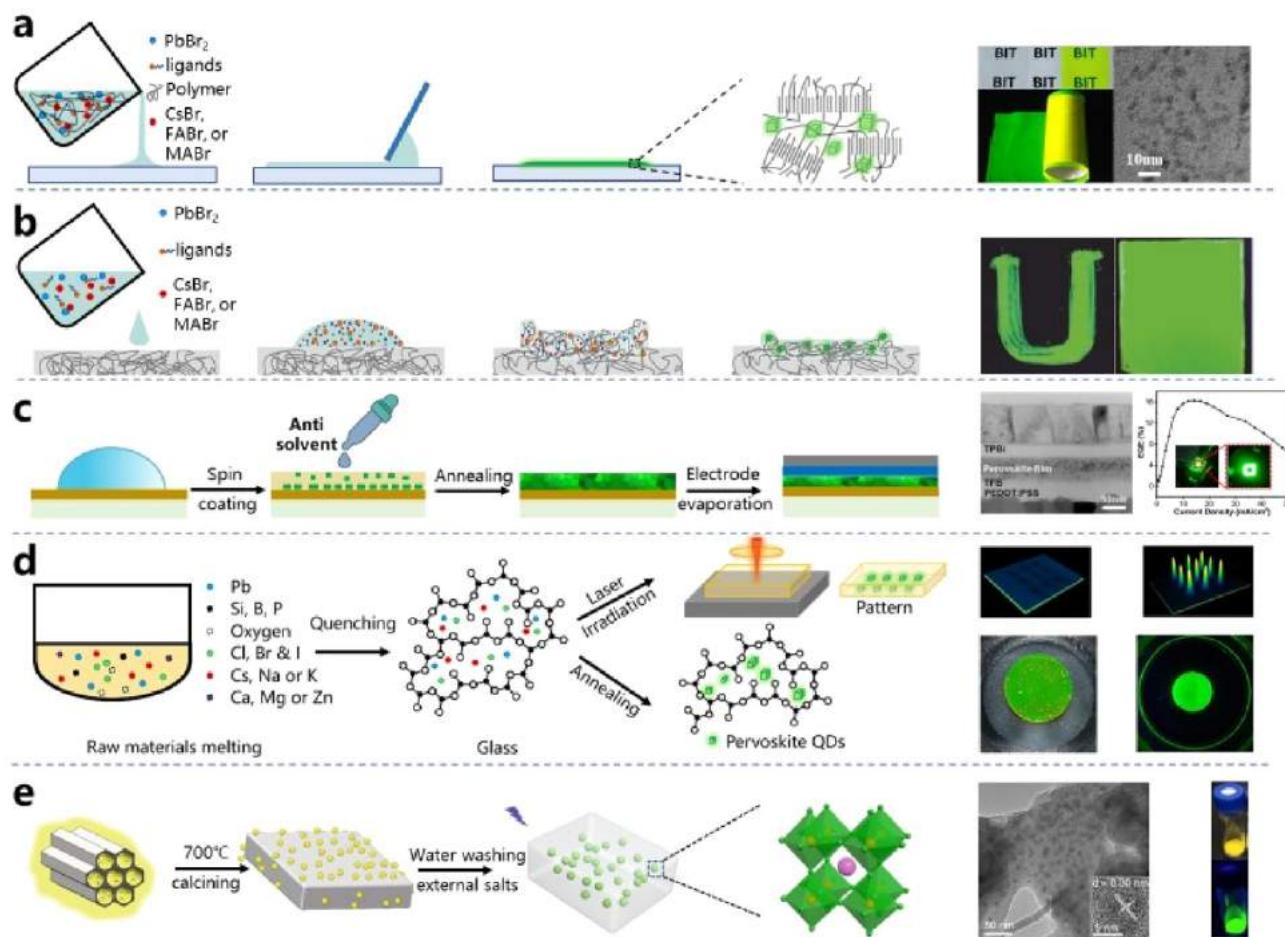


Figure 22. (a) Schematic illustration of the fabrication of perovskite NC composite by blade coating of precursor solution. The insets are the photographs of the luminescent film under sunlight and UV light and the TEM images of sliced films (right side). Reproduced with permission from ref 278. Copyright 2016 John Wiley & Sons, Inc. (b) Schematic illustration showing the fabrication of nanocomposites preparation with swelling–deswelling microencapsulation strategy. The insets are the images of the luminescent nanocomposite prepared by swab painting and spin coating under UV light (right side). Reproduced with permission from ref 285. Copyright 2016 John Wiley & Sons, Inc. (c) Schematic illustration of the fabrication of LED device based on NCs film prepared by *in situ* LARP progress. The insets are the TEM image of a device cross section and the plot of EQE vs current density of the device. Reproduced from ref 224. Copyright 2018 American Chemical Society. (d) Schematic illustration of the fabrication of perovskite NC glass composite and photographs of glass substrates having pattered NCs in the glass matrix (by either laser irradiation) and uniformly distributed NCs (by uniform annealing). The top panel on the right side reproduced with permission from ref 282. Copyright 2020 Nature Publishing Group. The bottom panel on the right side is reproduced with permission from ref 281. Copyright 2020 John Wiley & Sons, Inc. (e) Schematic illustration of perovskite NC-embedded molecular sieve phosphors. The insets are the TEM images and the photos of the phosphors under sunlight and UV light (right side). Reproduced with permission from ref 283. Reprinted with permission under a Creative Commons CC BY license. Copyright 2020 The Author(s).

diffusion-limited dynamics. Such different behavior was rationalized by the differences in ion sizes and mobilities. The anion exchange reaction in single-crystal perovskite nanoplates (with tens of micrometer lateral size) could be monitored by following the change in PL of individual platelets with a confocal microscope.²⁸⁸ Since this study was not done *in situ*, vapor-phase anion exchange reaction on dry CsPbBr_3 nanoplates was used that ensured rapid quenching of the reaction. At the intermediate stages of the anion exchange from CsPbBr_3 to CsPbI_3 , a coexistence of red and green emission peaks was observed in the PL spectra. Confocal PL maps recorded on nanoplates with different thicknesses and at different reaction times evidenced a gradual transformation from the edges toward the center of the plate, with dynamics that correspond to a diffusion-controlled mechanism.

The reversible reaction from CsPbCl_3 to CsPbBr_3 nanoplatelets was investigated by *in situ* PL spectroscopy by Wang *et al.*,²⁸⁹ revealing heterogeneity in the reaction kinetics that depend on the density of the exchanged ions in the crystals. By selecting different fields of view in the micro-PL measurements, the time traces of the emission of individual NCs were recorded, which manifested a strong dependence for the switching times on the concentration of substitutional halide ions used to induce anion exchange.

Heterostructure Fabrication via Anion Exchange. Anion exchange can be exploited to fabricate heterojunctions in lead-halide perovskite NCs. Huang *et al.* have shown in their progress report¹⁰⁶ a variety of lateral heterostructures in perovskite nanowires. CsPbBr_3 nanowires with different diameters were fabricated by wet chemistry, coated with poly(methyl methacrylate) (PMMA), and selected regions

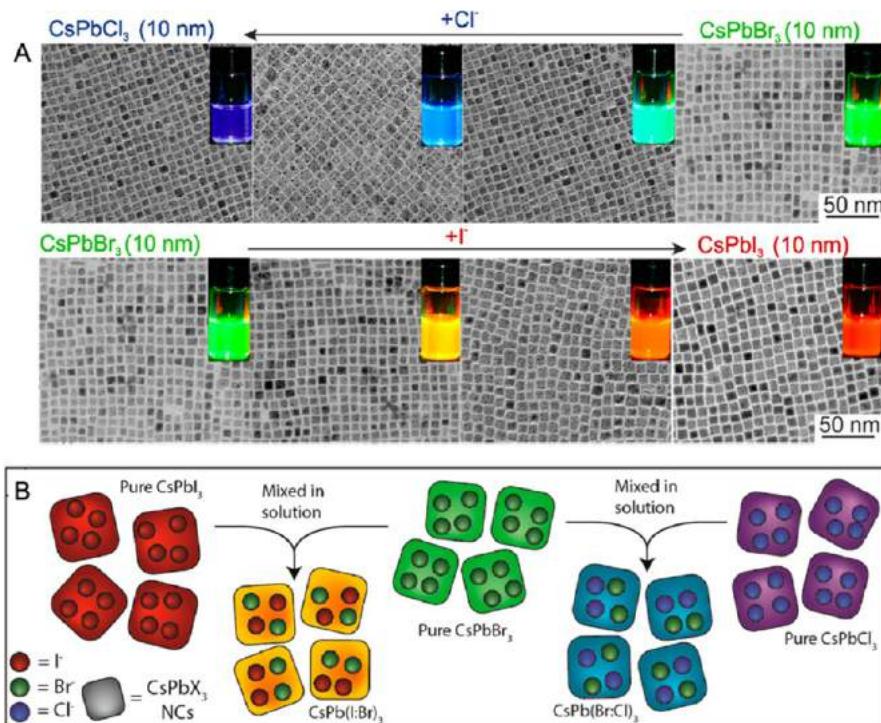


Figure 23. Post-synthesis halide exchange. (A) TEM images of CsPbX_3 nanocubes with mixed-halide composition. The insets show photographs of the colloidal solutions under ultraviolet light illumination. Reproduced from ref 55. Copyright 2015 American Chemical Society. Further permissions related to the material excerpted should be directed to the ACS. (B) Schematic illustration of the anion exchange reaction that occurs upon mixing NC solutions with different halides. Reproduced from ref 57. Copyright 2015 American Chemical Society. Further permissions related to the material excerpted should be directed to the ACS.

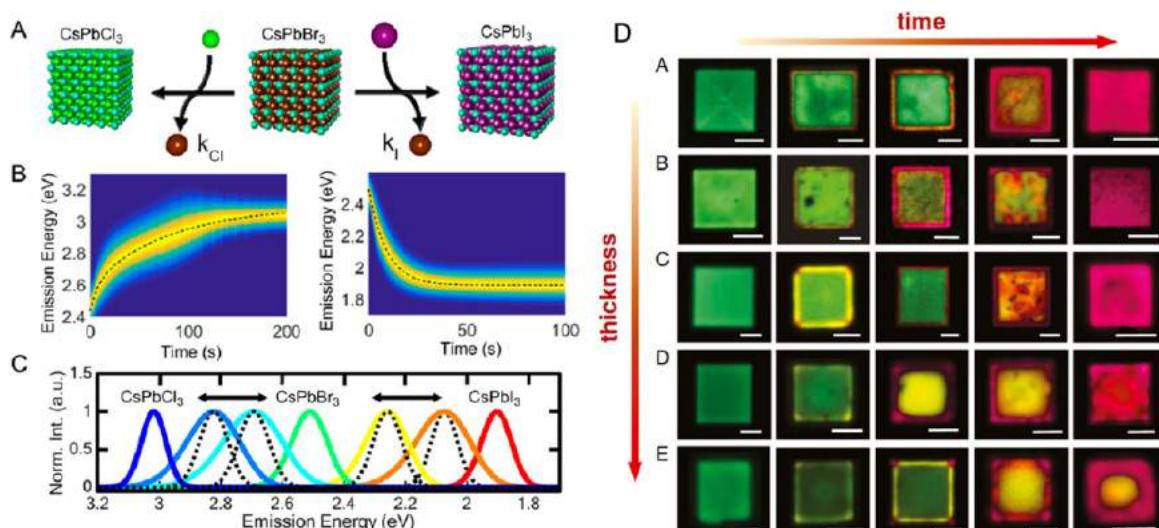


Figure 24. *In situ* photoluminescence monitoring during halide exchange reactions. (A) Schematic illustration of the exchange reaction. (B) PL spectra recorded from colloidal solutions during the anion exchange reactions. (C) PL spectra for the starting CsPbBr_3 NCs (green) and ending CsPbCl_3 (dark blue) or CsPbI_3 (red) along with spectra for mixed-halide compositions ($\text{CsPbBr}_{3-y}\text{I}_y$) in the both the kinetic (solid) and equilibrium (dashed) regime for each band gap shown. Panels A–C are reproduced from ref 287. Copyright 2016 American Chemical Society. (D) Confocal PL mapping of individual nanoplates for different thicknesses and reaction times. Reproduced with permission from ref 288. Copyright 2019 National Academy of Sciences of the United States of America.

were exposed by electron beam lithography. By applying anion exchange with chlorine and iodine precursor solutions, lateral heterojunctions with spatial resolution down to 500 nm were achieved and imaged by confocal fluorescence microscopy (Figure 25). Mixed-halide heterojunctions were also fabricated starting from CsPbBr_3 nanocubes with an anion exchange to CsPbI_3 and imaged by variable energy hard X-ray photo-

electron spectroscopy.²⁹⁰ These measurements elucidate, in contrast to a homogeneous alloy, that the anion exchange progresses *via* the formation of a heterojunction from the outer regions to inner regions of the nanowires, where the surface is rich with the exchanged anions and the core with the native ones. Even in fully exchanged nanocubes, a small core region containing the native (Br) anions was observed.

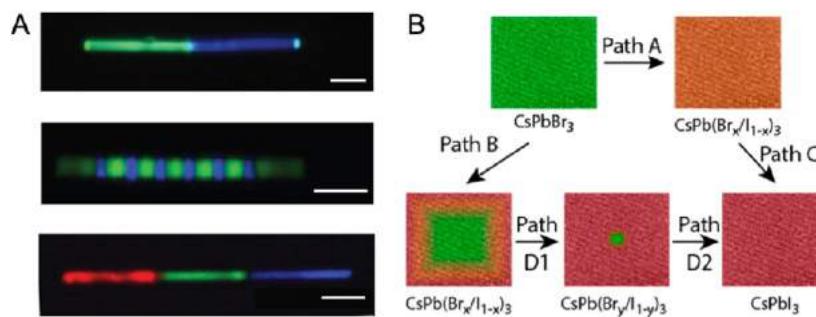


Figure 25. Heterojunctions fabricated by anion exchange reactions. (A) Heterojunctions obtained by masked anion exchange in a CsPbX_3 nanowire, leading to different halide compositions. Reproduced with permission from ref 252. Copyright 2017 National Academy of Sciences of the United States of America. (B) Schematic illustration of core–shell structures obtained by post-synthesis halide exchange. Reproduced from ref 290. Copyright 2018 American Chemical Society.

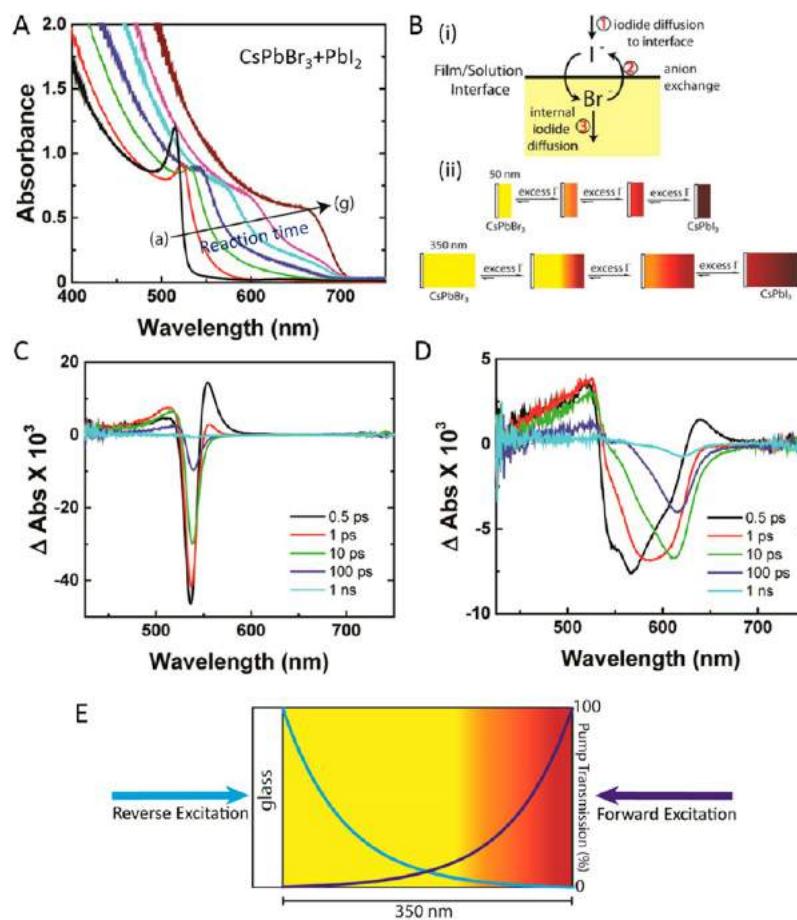


Figure 26. (A) UV–visible extinction spectra of CsPbBr_3 films (350 nm thick) soaked in PbI_2 solution at 120 °C for (a) 0, (b) 5, (c) 15, (d) 30, (e) 60, (f) 150, and (g) 480 min. (B) Schematic illustrations showing (i) three-step halide exchange reaction: iodide ions diffuses to the film–solution interface and exchanges with bromide, and the internal iodide diffuses away from the interface; (ii) differences in internal film structure of exchanged films of thickness 75 and 350 nm. (C,D) Transient absorption (TA) spectra of the 15 min soaked 350 nm thick film, acquired upon reverse (C) and forward (D) excitation. The TA spectra acquired under reverse excitation matches well with the steady-state absorption peak (panel A(d)), indicating that the signals originates from within the minimally exchanged portion of the thick film. Forward excitation gives rise a broad bleach spectra moving across the visible spectrum, indicating the excitation of the film surface at the compositional gradient. (E) Schematic representation showing the transient absorption experimental setup for study of thick film. The 387 nm pump can be completely absorbed by the film with an estimated penetration depth of 67 nm, leading to the significant differences in the position of the film where the pump is absorbed when exciting from the forward or reverse direction. Reproduced from ref 292. Copyright 2016 American Chemical Society. Further permissions related to the material excerpted should be directed to the ACS.

Colloidal atomic layer deposition has been employed to fabricate perovskite/metal oxide heterojunctions in NCs.²⁹¹ Here, for the case of alumina-coated CsPbBr_3 nanocubes, the oxide shell protected the perovskite NC core from anion

exchange reactions, which significantly increased the photoluminescence quantum yield and slowed down the kinetics of the anion exchange, which made monitoring by X-ray diffraction possible.

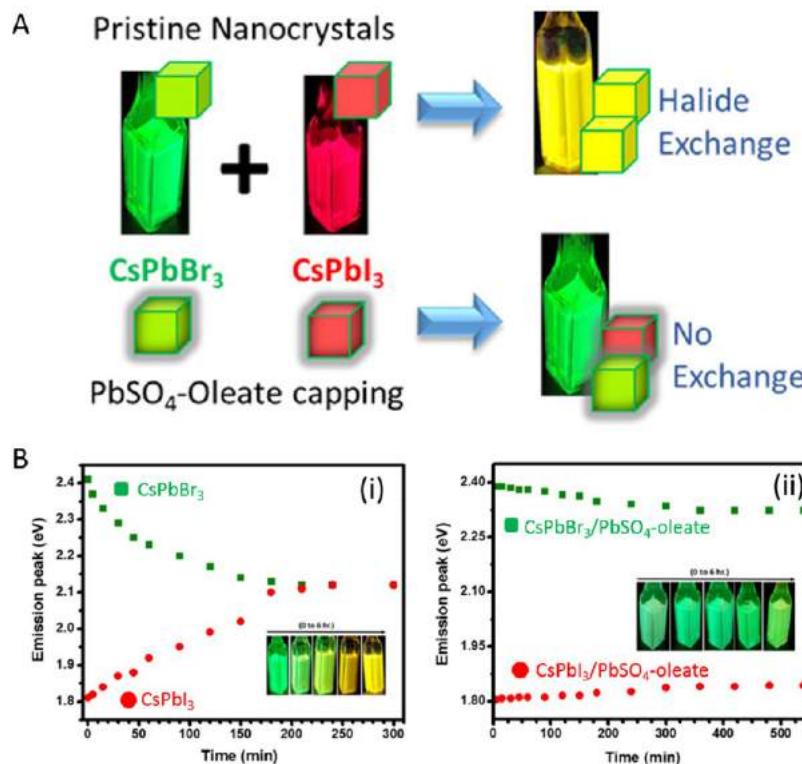


Figure 27. (A) Schematic illustration showing the halide exchange and no exchange with and without $\text{PbSO}_4\text{-oleate}$ capping. (B) Changes in photoluminescence peak energy with time of (i) pure CsPbBr_3 and CsPbI_3 NCs and (ii) $\text{PbSO}_4\text{-oleate}$ -capped CsPbBr_3 and CsPbI_3 NCs after mixing them in hexane solution. The insets show photographs of the colloidal NC mixture under UV light at various mixing times. Reproduced from ref 296. Copyright 2018 American Chemical Society. Further permissions related to the material excerpted should be directed to the ACS.

In another study, a sintered CsPbBr_3 nanocrystalline film was converted into a cubic CsPbI_3 film by exchanging bromide with iodide ions (Figure 26A). This approach enabled a gradient structure to be created with CsPbBr_3 at one side and CsPbI_3 on the other side of the film.²⁹² The exchange reaction proceeds through three steps, as illustrated in Figure 26B(i). The halide anion exchange rate is most likely governed by the anion exchange at the interface and the internal diffusion of newly formed iodide domain. In thinner films, the iodide ions can diffuse throughout the film, leading to a near-uniform film composition (Figure 26B(ii)). However, in the case of thick films, iodide ions cannot diffuse as fast as the additional iodide ions enter at the interface, causing a compositional gradient across the film (Figure 26B(ii)). Time-resolved transient absorption studies confirmed the migration of charge carriers from the high-band-gap CsPbBr_3 and $\text{CsPbBr}_x\text{I}_{3-x}$ regions to the iodide-rich region near the film surface with in few picoseconds after excitation (Figure 26C–E). The transient absorption spectra exhibited a narrow bleach upon reverse excitation (Figure 26C), which is consistent with steady state absorption spectra (Figure 26A). However, the bleach peak became broad when the excitation was switched to the forward side, and the peak shifted to lower energies with increasing time delay (Figure 26D). A time constant of 0.5 ps was estimated from the growth of bleaching of the iodide region. These differences in the transient absorption spectra were attributed to the inhomogeneous distribution of anions in thick films as compared to that of thin films after halide ion exchange (Figure 26E). Thus, the gradient films prepared through the halide ion exchange can direct charge carrier-funneling

behavior and could improve charge separation and transportation in optoelectronic devices. Because of the miscibility of different halides, such gradient structures are extremely sensitive to temperature and can quickly homogenize at higher temperatures.^{293,294}

Suppression of Anion Exchange. In many device applications, it is important that the anion exchange be suppressed between different layers of metal-halide perovskites. For example, in an all-perovskite tandem solar cell one would like to maintain the individual mixed-halide compositions in order to retain the aligned band structure of the films. The ease of halide exchange between different lead-halide perovskite films^{293,294} requires therefore the suppression of anion exchange. One such effective strategy is to cap $\text{CsPbBr}_x\text{I}_{3-x}$ NCs with $\text{PbSO}_4\text{-oleate}$ (Figure 27A). These capped NCs align linearly and can be deposited as films with a hierarchical nanotube architecture. The suppression of the halide ion can be seen in both NC suspension as well as multilayered films. For example, Figure 27B shows the emission changes during anion exchange and suppression of anion exchange with $\text{PbSO}_4\text{-oleate}$ capping of CsPbBr_3 and CsPbI_3 NCs. Moreover, Palazon *et al.* found that the CsPbX_3 NC films exposed to low flux of X-rays do not undergo halide anion exchange.²⁹⁷ This is because of the organic shell formed on the surface of NCs through intermolecular $\text{C}=\text{C}$ bonding within ligands upon exposure to X-rays. This approach enabled the fabrication of fluorescent patterns over millimeter scales with greater stability. By suppressing halide ion exchange, it was possible to mix lead-halide perovskite NCs and have a broader emission in the visible region of the spectrum,

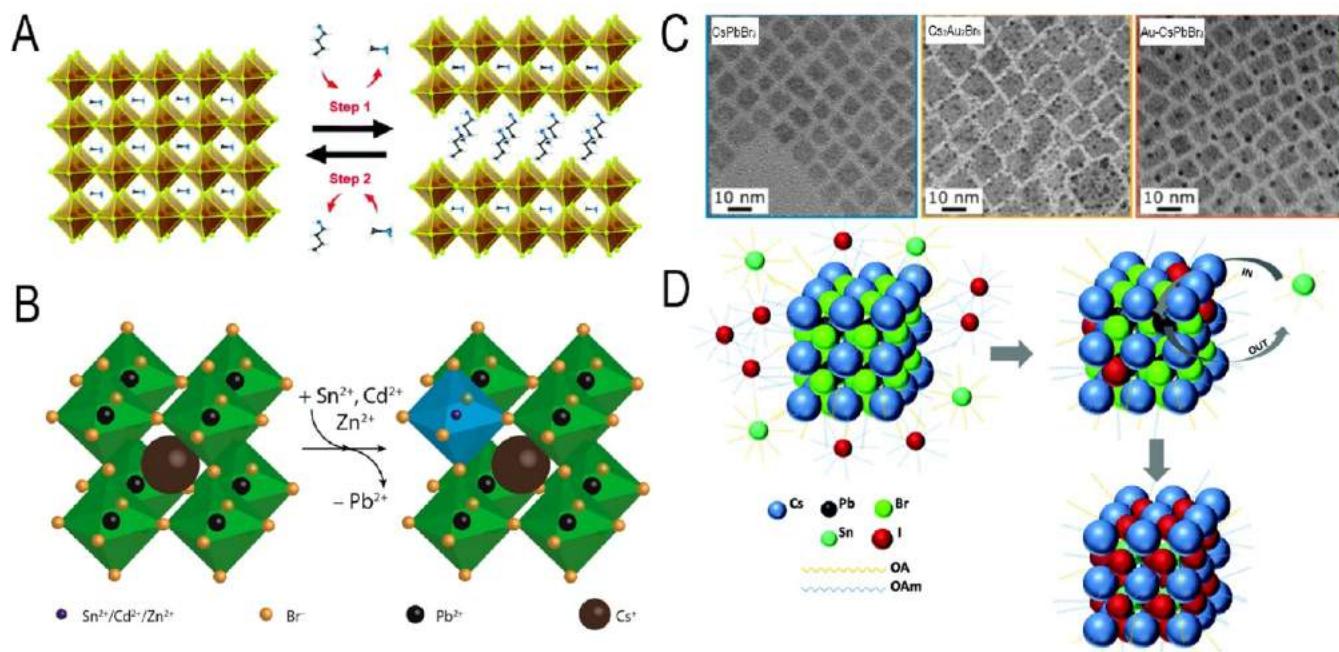


Figure 28. (A) Sketch of the “A” cation induced transformation of 3D to 2D perovskite structures, and back. Reproduced with permission from ref 302. Copyright 2018 Royal Society of Chemistry. (B) Partial “B” cation exchange in CsPbBr₃ NCs. Reprinted under CC-BY-NC-ND license from ref 304. Copyright 2017 American Chemical Society. (C) Competition between Au metal deposition and Pb²⁺ for Au³⁺ cation exchange in CsPbBr₃ NCs. From left to right: TEM images of starting CsPbBr₃ NCs, CsPbBr₃ NCs after Pb²⁺ for Au³⁺ cation exchange, CsPbBr₃-Au heterostructures. Reproduced from ref 305. Copyright 2017 American Chemical Society. (D) I⁻ anion driven Sn²⁺ cation exchange in CsPbBr₃ NCs. Reproduced with permission from ref 306. Copyright 2018 Royal Society of Chemistry.

including white emission.²⁹⁶ Significantly suppressed ion migration has also been achieved in layered perovskites.²⁹⁸

Cation Exchange. “A” Cation Exchange. One of the early observations of “A” cation exchange on halide perovskites was reported in a work describing halide anion exchange reactions in CsPbX₃ NCs by Akkerman *et al.*⁵⁷ In that work, various halide sources were explored to elicit anion exchange, starting from CsPbBr₃ NCs and going to CsPbCl₃ and CsPbI₃ (and back). On the other hand, exposing the CsPbBr₃ NCs to methylammonium bromide caused their PL to red shift from 2.43 to 2.36 eV, a value in line with that observed from MAPbBr₃ NCs. The exchange of Cs⁺ with MA⁺ was corroborated by the X-ray diffraction (XRD) pattern of the sample after the reaction, which indicated a lattice expansion, compatible with the larger size of the MA⁺ cation compared to Cs⁺. It is interesting to note that exchange of the Cs⁺ cation with smaller cations (Rb⁺, K⁺) attempted by Nedelcu *et al.*⁵⁵ led instead to the decomposition of the NCs. This was rationalized by hypothesizing that the cation sublattice in halide perovskites is much more rigid than in other compounds, for example, metal chalcogenides, where instead cation exchange occurs easily.²⁹⁹ A partial methylammonium (MA⁺) to formamidinium (FA⁺) cation exchange was also observed by Xie *et al.*³⁰⁰ during the deposition of a film of MaPbI₃ from a solution containing both MA⁺ and FA⁺ cations: even though MaPbI₃ was formed first, it evolved in 2 min to FA_{0.85}MA_{0.15}PbI₃, a composition that was observed to stabilize the α -phase.

Partial “A” exchange, followed by a phase transformation, was reported by Wang *et al.*,³⁰¹ who treated CsPbBr₃ NCs with rubidium-oleate. The exchange of Cs⁺ with Rb⁺ ions was limited to the surface of the NCs. Also, it was accompanied by a phase transition to the Rb₄PbBr₆ structure, leading to the

formation of core/shell CsPbBr₃/Rb₄PbBr₆ NCs with improved stability and enhanced PLQY compared to the core “only” CsPbBr₃ NCs. Another example of “A” exchange triggering a phase transformation is the one provided by Huang *et al.*,³⁰² who started from MAPbBr₃ NCs and reacted them with phenethylammonium bromide (PEABr). The large size of the PEA⁺ cations makes the 3D perovskite phase unstable, hence their introduction in the lattice causes a transition to the layered phase, accompanied by a blue shift of the emission to 411 nm, as the layered material has a higher band gap than MAPbBr₃ (Figure 28A).³⁰² The reverse reaction took place when MA⁺ ions were added to the 2D NC solution (Figure 28A).³⁰² Partial exchange of MA⁺ ions with Cs⁺ ions in films of MAPbI₃ was found to be essential to preserve the black γ -phase and therefore to avoid the detrimental transition to the higher band gap δ -phase, which is undesirable for photovoltaic applications.³⁰³ In addition, the resulting films were compact and pin-hole-free and the solar cells fabricated from such films had a power conversion efficiency of 14.1%.

“B” Cation Exchange, “Partial” versus “Full”. Initial attempts by Nedelcu *et al.*⁵⁵ to exchange the “B” cation in NCs were unsuccessful (Ba²⁺, Sn²⁺, Ge²⁺, etc.), as the NCs were dissolved. The initial report on successful “B” cation exchange is by van der Stam *et al.*,³⁰⁴ who could partially replace Pb²⁺ ions with various bivalent M²⁺ cations (Sn²⁺, Cd²⁺, Zn²⁺), with no major changes in the size and shape of the NCs, except for a small shrinkage due to the contraction of the unit cell, as all these cations have smaller ionic radii compared to Pb²⁺ (Figure 28B). The lattice contraction was also invoked as an explanation for the blue shift in the optical spectra (with preservation of PLQY at values over 50%) following the partial “B” cation exchange. Extensive analysis of the samples showed that the guest cations were homogeneously distributed in the

NCs. The extent of the exchange was such that roughly up to 10% of the Pb^{2+} cations could be replaced. These reactions are limited by the low diffusion rate of the cations in the perovskite lattice, especially for the “B” cation.³⁰⁷ Although the reaction should be favored by the increase in entropy arising from the formation of a $\text{CsPb}_{1-x}\text{M}_x\text{Br}_3$ solid solution, van der Stam *et al.* argued that the replacement of Pb^{2+} ions with smaller cations progressively builds up compressive strain in the lattice, which tends to counter any further exchange,³⁰⁴ thus making the overall process self-limited. Another interesting point made by van der Stam *et al.* is that the cation exchange should be promoted by the presence of halide vacancies (which have low formation energies), so that any exogenous factor limiting the formation of such vacancies should also limit the exchange.³⁰⁴ In this regard, the authors considered alkylamine molecules, with their binding ability to Br^- ions, as being responsible for preserving a high density of Br vacancies in the NCs, through their ability to remove Br^- ions from the NCs. However, when working with large concentrations of MBr_2 in solution (in the attempt to further promote Pb^{2+} for M^{2+} exchange), the amines lose this “extracting” capability (as there are already too many Br^- ions in solution), and the exchange slows down considerably.

Reversible partial “B” cation exchange was observed by Gao *et al.* when reacting CsPbCl_3 NCs with Mn^{2+} ions, leading to $\text{CsPb}_{1-x}\text{Mn}_x\text{Cl}_3$ NCs or even starting from CsMnCl_3 NCs and reacting them with Pb^{2+} ions.³⁰⁸ This latter case is similar to that of Fang *et al.*,³⁰⁹ who also started from rhombohedral CsMnCl_3 NCs and reacted them with PbCl_2 , thus forming hexagonal $\text{Cs}_4\text{Pb}_x\text{Mn}_{1-x}\text{Cl}_6$ NCs as the intermediate and then cubic $\text{CsPb}_x\text{Mn}_{1-x}\text{Cl}_3$, hence undergoing through successive phase transitions during the exchange.

The hypothesis that only partial “B” cation exchange is possible in halide perovskites was actually challenged by Eperon *et al.*,³¹⁰ who started from films of formamidinium tin triiodide ($\text{CH}(\text{NH}_2)_2\text{SnI}_3$, *i.e.*, FASnI_3), which could be either partially or fully converted to FAPbI_3 . The preservation of the morphology of the films proved that this conversion did not proceed through dissolution–recrystallization but was indeed a topotactic exchange reaction. In the same work, the reverse exchange (from Pb to Sn) was demonstrated, as well, and the same processes were extended to colloidal NCs.³¹⁰ The work demonstrated that the “B” cations, at least in selected cases, are actually mobile, thus providing a starting point for possible studies in which transient effects stemming from such B cation mobility may be identified by appropriate experimental tools.

Another notable report on “B” cation exchange is the work of Roman *et al.*³⁰⁵ (Figure 28C). In their case, the exchange was actually an undesired reaction, as they were attempting to deposit an Au metal domain on top of CsPbBr_3 NCs by adding Au^{3+} ions, in a reducing environment provided by the surfactant molecules (oleic acid and oleylamine). The exclusive formation of Au– CsPbBr_3 heterostructures was possible only if PbBr_2 was added together with the Au^{3+} ions, so that Pb^{2+} could efficiently outcompete the Au^{3+} and Au^+ ions in the exchange with the Pb^{2+} ions already present in the NCs. Indeed, when no PbBr_2 was added, a significant side reaction was the replacement of Pb^{2+} ions by couples of $\text{Au}(\text{I})$ and $\text{Au}(\text{III})$ ions, leading to the formation of double perovskite $\text{Cs}_2\text{Au}^{\text{I}}\text{Au}^{\text{III}}\text{Br}_6$ NCs with tetragonal crystal structure, decorated by Au domains.

Simultaneous Anion–Cation Exchange. There are several reports on concomitant anion–cation exchange. For instance,

Li *et al.*³¹¹ started from Mn^{2+} -doped CsPbCl_3 NCs (written as $\text{CsPb}_{1-x}\text{Cl}_3\text{:xMn}^{2+}$), which were reacted with ZnBr_2 , such that $\text{CsPb}_{1-x-z}\text{Zn}_z(\text{Cl}_y\text{Br}_{1-y})_3\text{:xMn}^{2+}$ NCs were obtained. Hence, in this type of reaction, the Pb^{2+} (and indeed also Mn^{2+}) ions were partially exchanged with Zn^{2+} and the Cl^- ions with Br^- . The motivation in that work was to fabricate a system in which the concentration of Mn^{2+} dopants is still high (so that there is strong emission from Mn^{2+} -derived states), and that at the same time the lattice is rich in Br^- ions. Apparently, it is not possible to reach high Mn^{2+} doping levels in Br^- -dominant CsPbX_3 hosts, but the additional presence of Zn^{2+} ions made it possible.

Various groups have actually observed that the rate of cation exchange is significantly accelerated if also anions are simultaneously exchanged, a process that has been named “anion-driven cation exchange”. In one of the early observations of this type, CsPbBr_3 NCs were reacted with SnI_2 and they quickly transformed to CsSnI_3 (a process which however broadened the size distribution), going through intermediate $\text{CsPb}_x\text{Sn}_{1-x}(\text{Br}_{1-y})_3$ compositions (Figure 28D).³⁰⁶ A much lower reactivity was observed instead toward SnBr_2 . An interesting case of anion-driven cation exchange is the one described by Qiao *et al.*³¹² who used light to trigger the degradation of dihalomethane in a solution containing CsPbX_3 NCs ($\text{X} = \text{Cl}, \text{Br}$) and a sub-micromolar concentration of Mn acetate. The photodegradation reaction released halide ions, which triggered halide and Pb^{2+} to Mn^{2+} exchange at the same time. This process was named “photoinduced doping”.

A different approach, which can be nonetheless still considered as a sort of anion-assisted exchange, is the one described by Zhou *et al.*,³¹³ in which CsPbCl_3 NCs were effectively doped with Mn^{2+} ions when, in the one-pot synthesis of the NCs, trimethylchlorosilane (TMS-Cl) was present in addition to Mn acetate. The authors of the work argued that the high bond dissociation energy of the Mn–O bond in Mn acetate severely limits the availability of Mn^{2+} ions in solution and hence their possibility to be incorporated in the CsPbBr_3 NCs. On the other hand, the rapid degradation of TMS-Cl frees a large amount of Cl^- ions, and as a consequence, octahedral $[\text{MnCl}_6]^{4-}$ complexes are formed in solution (in addition to $[\text{PbCl}_6]^{4-}$ complexes). These units are then directly inserted in the NCs as they nucleate and grow. The general applicability of this reaction scheme was demonstrated by extending the doping to other divalent transition metal cations ($\text{Ni}^{2+}, \text{Cu}^{2+}$, and Zn^{2+}).³¹³

Doping strategies aim at conferring additional physical properties to the perovskite materials, but they can also impart higher structural, chemical, and photochemical stability (including improved PLQY). A recent case was disclosed by Shapiro *et al.*,³¹⁴ who also exploited an anion-driven cation exchange on CsPbBr_3 NCs, using NiCl_2 (or NiBr_2), and were able to prepare Ni-doped $\text{CsPb}(\text{BrCl})_3$ NCs, with Ni concentrations tunable from below 1% up to 12% and higher PLQY than that of the starting NCs. When using NiCl_2 , compositional analysis showed that the extent of halide exchange was much higher than that of cation exchange. For example, to a Ni doping of 5.6% corresponded a 50:50 ratio of Br/Cl . This evidenced that, although halide ions are key to ensure the Pb^{2+} to Ni^{2+} exchange, the latter reaction still proceeds at a rate much lower than that of the concomitant anion exchange.

Post-synthetic Nanocrystal Shape Transformations. Post-synthetic shape transformations provide access to

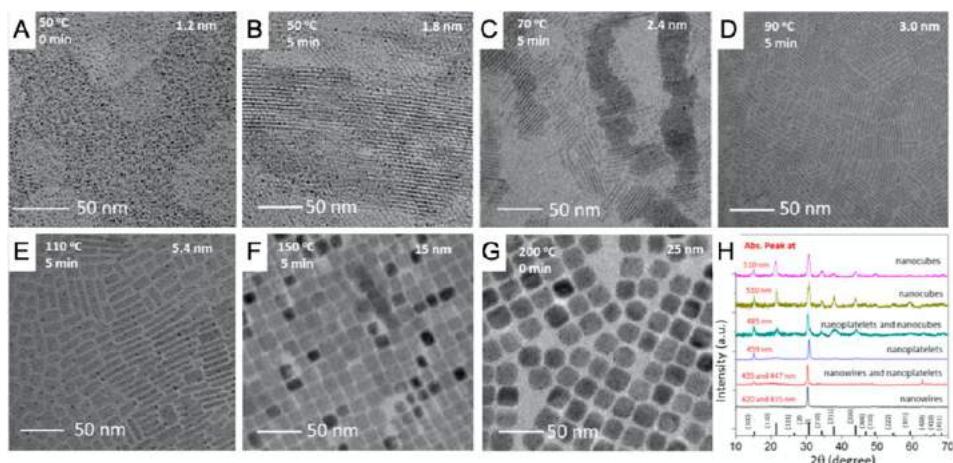


Figure 29. Shape transformations occurring during CsPbBr_3 NC synthesis for different temperatures and reaction times. (A–G) TEM images. (H) X-ray diffraction data. Reproduced from ref 316. Copyright 2018 American Chemical Society.

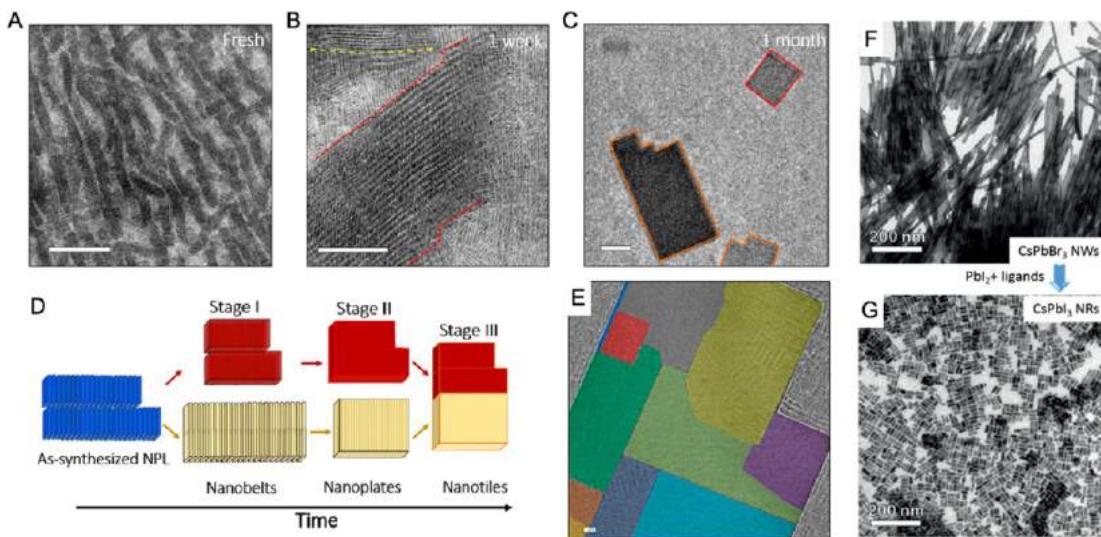


Figure 30. Temperature and chemically induced transformations in shape of CsPbBr_3 NC structures. (A–C) TEM images recorded from aliquot taken from CsPbBr_3 nanoplatelet solution at different times. (D) Illustration of the oriented assembly process and transformation from nanoplatelets to nanobelts, nanoplates, and nanotiles. (E) False-colored TEM image of a nanotile. Panels A–E are reproduced under Creative Common CC-BY 4.0 license from ref 319. Copyright 2020 American Chemical Society. (F,G) Chemical cutting of CsPbBr_3 NWs into CsPbI_3 nanorods. Reproduced with permission from ref 73. Copyright 2018 John Wiley & Sons, Inc.

colloidal NCs that are difficult to obtain by direct synthesis. In addition, they help to understand the growth mechanism and the properties of the corresponding NCs. Attempts to improve the properties of nanocube-shaped perovskite NCs by post-synthesis annealing revealed that such heat treatments can lead to changes in the NC shape and size. Yuan *et al.*³¹⁵ observed a red shift of the photoluminescence wavelength accompanied by a degradation in intensity upon thermal annealing under vacuum at a temperature of 400 K. TEM imaging revealed an increase in NC size of up to a factor of 2 to 3, and compositional analysis showed that the Pb/Br ratio decreased, thus pointing to more Br-rich surfaces after annealing. The impact of the temperature on the NC growth and shape transformations was elucidated in detail by Pradhan and co-workers (Figure 29).³¹⁶ By stepwise increasing the temperature in their reactions, they demonstrated highly accurate size control and observed shape transformations from thin nanowires to nanoplatelets in the early stages of the reaction that evolved into nanocubes with dimensions up to 25 nm for

longer reaction times. Tong *et al.*²² found that CsPbBr₃ nanocubes could gradually transform into nanowires through an oriented attachment mechanism under specific reaction conditions. A similar shape transformation was reported by Sun *et al.*,¹⁸⁶ who showed that cubic crystalline CsPbI₃ nanocubes transform into nanowires upon their treatment with polar solvents. The authors attributed this to polar solvent induced lattice distortions in cubic crystalline CsPbI₃ nanocubes, followed by dipole-moment-triggered self-assembly into single-crystalline NWs. Similarly, Pradhan *et al.*³¹⁷ showed that post-synthetic aging of colloidal solutions leads to the transformation of CsPb(Br_xI_{1-x})₃ into the corresponding NWs with length up to several micrometers. Such shape transformation can also be triggered by halide-vacancy-driven, ligand-directed self-assembly process, as demonstrated by Bakr and co-workers.³¹⁸ They have shown that the halide vacancy CsPbBr₃ nanocubes transform into millimeter-long NWs upon ligand exchange with didodecyldimethylammonium sulfide (DDAS).

The evolution of CsPbBr_3 nanoplatelets into nanobelts, nanoplates, and nanotiles over time in solution and in films was investigated in detail by Dang *et al.*³¹⁹ (Figure 30A–E), who evidenced the formation of nearly defect-free nanobelts at the early stage by oriented attachment and fusion of the nanoplatelets, while at later stages, the nanobelts and nanoplates assembled into mosaic-like nanotiles. The interfaces in such nanotiles were characterized by Ruddlesden–Popper stacking faults due to the presence of CsBr bilayers. This transformation, which occurred in solution at room temperature over several weeks, was also observed in thin NC films and could be accelerated to time frames of less than 1 h by increasing the temperature. Around the same time, Pradhan and co-workers reported a similar shape transformation on a TEM grid at RT.³²⁰ They found that the polyhedral nanocubes transform into either zigzag-shaped 1D nanostructures by oriented attachment of corners or nanotiles by sidewise fusion, depending on their composition. Interestingly, these transformations could be ceased at any point of time either by applying heat or by adding sufficient ligands. A similar transformation had been reported earlier by Shamsi *et al.*,²³⁴ who found that the exposure of CsPbBr_3 nanoplatelet films to intense ultraviolet light led to the transformation into nanobelts. Since the initial nanoplatelets were blue emitting due to quantum-confinement effects, while the larger nanobelts emitted green light, the use of shadow masks in such transformation could lead to color patterned films. The high brightness and stability of the films that were exposed to ultraviolet light enabled the fabrication of solution-processed light-emitting diodes. Such light-induced shape transformations strongly depend on the type of surface ligands. Li *et al.*³²¹ showed that individual CsPbBr_3 perovskite NCs capped with 1-alkynyl acids could readily transform either into large cuboid- or peanut-shaped microcrystals under UV irradiation. The shape of the resultant microcrystals depend on the chain length of the 1-alkynyl acid used as surface ligand. The authors proposed that the shape transformation was caused by self-assembly of CsPbBr_3 nanocubes through ligand-induced homocoupling of surface ligands. In addition, the transformation of nanocubes to nanoplates has also achieved by applying pressure in the GPa range (in a diamond anvil cell) to superlattices of CsPbBr_3 nanocubes.³²² The pressure treatment led to the formation of nanoplates with edge lengths that were 2–3 times larger than those of the initial nanocubes and to a blue-shifted emission after pressure release, pointing to quantum confinement in the out-of-plane direction.

Transformations *via* fragmentation of perovskite NCs, instead of assembly, is another possible mechanism. Tong *et al.*⁷³ demonstrated the chemical cutting of CsPbBr_3 by a ligand induced fragmentation into CsPbX_3 nanorods (X = Cl, Br, I) that was triggered by a halide anion exchange reaction (Figure 30F,G). The emission of the resulting perovskite nanorods could be tuned across the visible range, and photon antibunching experiments revealed single-photon emission from such nanorods. Other ligand-induced post-synthesis transformations include the evolution of CsPbBr_3 nanocubes to NWs and 0D structures, or to nanoplates.³²³ In this latter work, the transformation could be controlled by the choice of the ligands: alkyl carboxylic acids lead to emitting nanoplates, while oleylamine and octylamine initiated the formation of NWs and 0D structures. On the other hand, shape transformations have been rarely reported for OIHP NCs. For instance, Tong *et al.*²³¹ demonstrated the ligand-induced

transformation of 3D nanocubes into 2D NPIs upon dilution of colloidal solution. They showed that the thickness of the NPIs is tunable by both the ligand concentration as well as the dilution level. In addition, nanoplatelets could be obtained by bottom-up shape transformation of spherical nanodots, as reported by Liu *et al.*³²⁴ They showed that the nanodots obtained by LARP gradually transform into square shape NPIs upon aging the nanodot solution for 3 days. They attributed this transformation to dipole–dipole interactions along with realignment of dipolar vectors of nanodots.

Summary and Outlook of Shape and Composition-Controlled Synthesis of LHP NCs. Numerous methods have been reported for the shape-controlled synthesis of both OIH and inorganic colloidal LHP NCs. Most of the reported methods generally yield either nanocubes, nanoplatelets, or nanowires. Recent studies have demonstrated the synthesis of noncubic LHP NCs at relatively high reaction temperature.^{70,71} However, these methods are yet to be standardized for the routine synthesis of noncubic LHP NCs. The shape of the LHP NCs is controllable from nanocubes to NPI of different thicknesses by varying several parameters, such as reaction temperature,¹⁸ precursor ratio,⁶⁰ long-chain to short-chain ligands ratio,¹⁶ and acid–base equilibrium of ligands.¹⁴⁵ In general, lower reaction temperatures lead to anisotropic growth of NCs, and this results in the formation of LHP NPI at reaction temperatures below 100 °C, and the thickness of NPIs decreases with decreasing the reaction temperature.¹⁸ On the other hand, LHP nanocubes transform into nanowires under prolonged reaction times in both the HI synthesis and the ultrasonication-assisted synthesis.^{22,75} The transformation of nanocubes into nanowires occurs through an oriented attachment mechanism.^{22,186,318} Furthermore, the thickness of the nanowires is tunable down to the strong quantum-confinement regime using short-chain ligands.^{74,76} In addition, shape control is achieved through post-synthetic transformations. For example, it was shown that NPIs could be transformed into nanosheets,³¹⁹ and nanowires could be transformed into nanorods.⁷³ Despite significant advances in the synthesis of LHP NCs, their growth mechanism is still not well-understood due to the fast nucleation and growth processes, which are therefore hard to follow. A better understanding of their growth mechanism is critical for further advancing the synthesis of LHP NCs of desired shapes through controlled growth rate and directionality using specific ligands. The optical band gap of LPH NCs mainly depends on the extent of the quantum confinement that the NCs exhibit, and this is discussed in detail in the optical properties section (see **OPTICAL PROPERTIES**). The optical properties of LHP NCs are easily tunable across the visible spectrum of light by halide (Cl, Br, and I) composition, and they can be prepared either by direct synthesis or by applying halide ion exchange reactions. The distinctive feature of LHP NCs is that the halide ion exchange is spontaneous and reversible, and it takes place at room temperature. This means LHP NCs with any halide composition can be easily achieved using presynthesized LHP NCs made of any one of the halide types. For some applications, such a spontaneous halide exchange can be problematic. However, the halide exchange could be suppressed by coating LHP NCs with lead sulfates.²⁹⁶ In addition, good progress has been made regarding the cation (A- and B-site) exchange of LHP NCs for enhancement of their stability, for the sake of introducing additional optical properties and replacing Pb with nontoxic metal ions.

SURFACE CHEMISTRY OF COLLOIDAL HALIDE PEROVSKITE NCs

With the decrease of particle size down to several nanometers, the fraction of surface atoms in NCs can be higher than 30%. The incomplete coordination of surface atoms usually contributes to the appearance of defect energy levels in the band gap that behave as exciton traps and leads to nonradiative recombination.^{325,326} Therefore, in past decades, researchers from the field of II–VI semiconductor NCs (mainly the cadmium-based NCs) have made great efforts to solve this problem. Finally, PLQY of 100% and perfect monoexponential PL decay were achieved by an elaborate design of synthesis procedures and shell structures.^{327,328} However, lead-halide perovskite NCs with a high QY (~100%) can be prepared directly and easily even without shells.^{14,329,330} This phenomenon is related to the high defect tolerance of these materials.^{98,331} Theoretical calculations have suggested that the defects with low formation energies are the ones that contribute to shallow states. A detailed discussion on defect tolerance and the distinctive emission properties of lead-halide perovskite NCs is provided in the optical properties section.

After several years of research, it was found that the surface defects, especially the halide vacancies (V_X), still make great contributions to nonradiative recombination. Then, various passivation strategies were developed to enable a PLQY for perovskite NCs close to 100%. As a whole, these passivation approaches can be divided into two types: post-synthesis passivation and *in situ* passivation, that is, during the synthesis (see below). It should be noted that crystal defects in NCs can be eliminated by a self-purification mechanism.³³²

Surface Ligands. Lead-halide perovskite nanomaterials typically consist of an all-inorganic or organic–inorganic core, such as $CsPbX_3$ and $CH_3NH_3PbX_3$ ($X = Cl, Br, I$) NCs, capped with organic ligands, and we will refer to them as LHP@capping NCs. The interest of focusing on surface chemistry of LHP NCs is to better understand the interaction between the ligand anchoring group(s) and the NC surface in LHP@capping NCs with a view to finding the most suitable ligands for surface passivation, thereby manifesting the best of the distinctive properties of the perovskite, thus enhancing their applicability.

Ligands play a crucial role during the synthesis of the NCs, such as in the kinetics of the crystal growth and in regulating the final NC size and shape.^{52,333} In addition, the capping ligands can be designed to prevent the agglomeration of the NCs and determine the extent of the NC–solvent interaction and, consequently, their dispersibility in the medium.^{52,333,113} However, the high dynamic bonding between the NC surface and the capping ligands is at the origin of the chemical instability of LHP@capping NCs; this has become patent during the purification of these nanomaterials.^{52,177} Therefore, enhancing the strength of the ligand coordination to the NC surface can have a positive impact on the colloidal and chemical stability of the NCs and, consequently, on the conservation of their optical properties. Nevertheless, another important feature of the ligand that has to be taken into account is its electrical conductivity, as efficient charge carrier transport is required in NC thin-film-based optoelectronic devices. Lately, this matter has attracted a great deal of interest.^{334,335}

Techniques to visualize the dissociation of the ligands from the NC surface, as well as the nature of the ligand anchoring


group, are providing relevant information to find the most adequate ligand, or combination of ligands, to exploit the distinctive properties of these materials at the nanoscale.^{84,336} The combination of spectroscopic techniques, such as NMR, FTIR, and XPS, are useful to determine the eventual ligand(s) on the NC surface and the nature of the ligand anchoring group(s). In addition, the combination of NMR spectroscopy and thermogravimetric analysis (TGA) is a suitable strategy to study the composition of LHP@capping.²⁵ The ionic nature of these NCs makes them revert back to the NC precursors in a polar solvent, such as deuterated DMSO, thus making it possible to know the structure of the ligand(s) bonded to the surface and to determine the ratio between the LHP@capping components easily by 1H NMR.²⁵ In addition, the combination of NMR, nuclear Overhauser effect spectroscopy (NOESY), and diffusion-ordered spectroscopy (DOSY) makes it possible to determine if the organic ligand is loosely or tightly bound at the NC surface.⁸⁴ Moreover, the NMR line broadening technique is also of interest for surface chemistry analysis and has been related to poor ligand solvation, a feature of bound ligands.³³⁷ The broad line has a homogeneous and a heterogeneous component. Solvation of the ligand shell contributes mainly to the heterogeneous line broadening, as was confirmed by dynamic simulations, while the homogeneous contribution depends on the NC size (the bigger the size, the broader the line).³³⁸ Despite significant understanding of the ligand–NC interaction over the last few years, there are still some issues to be overcome to improve the potential of colloidal perovskite NCs in different technologies. Several contributions will be discussed below.

Passivation of Surface Defects with Ligands. The type of ligand binding to the surface of common semiconductor NCs has been analyzed using the covalent bond classification introduced by Green *et al.* for organometallic compounds.^{339,340} In this model, the covalent bond of any element is classified according to the total number of electrons involved in the primary bonding in the valence shell of the element (M) and the number of electrons the ligand used to form the bond.

Three types of binding ligands were reported: (a) X-type, which involves a single occupied orbital of the ligand anchoring group and one electron from M (the ligands are neutral species that are radicals, such as H, COR, CR₃, C₆H₅, CN, OCN, ONO; X ligands can derive from anionic precursors, such as halides, hydroxide, alkoxide alkyl species that are one-electron as neutral ligands, but two electron donors as anionic ligands); (b) L-type, which involves an orbital of the ligand filled with two electrons and acts as a donor to the empty orbital of M (the ligands are neutral molecules that are Lewis bases, such as NH₃, NR₃, OH₂, OR₂, PR₃, SR₃); and (c) Z-type, whose anchoring group orbital is empty and can accept an electron pair from M (the ligands are neutral molecules that are Lewis acids, such as BH₃, BF₃, BCl₃).^{339,340}

Regarding the type of ligands in LHP@capping NCs, the most common ligands used are of X- and L-type (see **Scheme 1**). The binding of ligands to the surface of these NCs is usually highly dynamic and therefore ligands can be lost during the isolation and the subsequent purification steps. Highly emissive LHP@capping NCs are the consequence of an efficient passivation of their surface defects with ligands that anchor to the NC surface with a high binding constant, which are mainly of the X- and L-types, thus providing colloidal and chemical stability. The binding mechanism of the ligands ranked by the covalent bond classification can be summarized

Scheme 1. Binding Ligands (X, L, and Z-Type, According to the Covalent Bond Classification) Used as Capping Agents of Colloidal APbX_3 Perovskite NCs

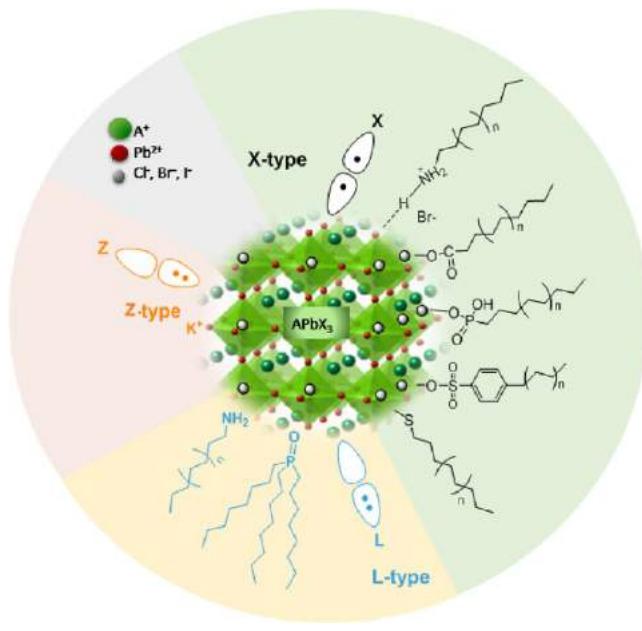

as (i) X-type ligand: covalent bond created after one electron donation from the halide anion to the ammonium, or from the carboxylate, phosphate, sulfonate, or thiol/thiolate to the perovskite cations (Pb^{2+} , A^+), or between the charged groups of a zwitterionic molecule and X^- and Pb^{2+} ; (ii) L-type ligand: dative covalent bond created by sharing a lone electron pair from the ligand with the metal center; and (iii) Z-type ligand: dative covalent bond by sharing a lone electron pair from the halide with a Lewis acid, such as the interaction between K^+ and X^- .



















In 2012, Papavassiliou *et al.* described the preparation of nanocrystalline/microcrystalline materials based on $\text{Pb}(\text{Br}_x\text{Cl}_{1-x})_3$, $\text{Pb}(\text{Br}_x\text{I}_{1-x})_3$, $\text{Pb}(\text{Cl}_x\text{I}_{1-x})_3$ units with $x = 0\text{--}1$, which exhibit tunable emission from 400 to 700 nm, from the corresponding quasi-two-dimensional compounds.⁶⁴ Suspensions based on lead bromides materials were obtained using a titration-like method, in which the solutions of $(\text{CH}_3\text{NH}_3)^+(\text{CH}_3\text{C}_6\text{H}_4\text{CH}_2\text{NH}_3)_2\text{Pb}_2\text{Br}_7$, $(\text{CH}_3\text{NH}_3)(\text{C}_4\text{H}_9\text{NH}_3)_2\text{Pb}_2\text{Br}_7$, or their precursors in dimethylformamide were injected into toluene or toluene-containing PMMA, at room temperature. The crystalline particles presented sizes ranging between 30 and 160 nm and green emission in the 531–510 nm range with PL quantum yield from 0.13 to 16%. These values were improved up to 25% using $(\text{CH}_3\text{NH}_3)(\text{C}_4\text{H}_9\text{NH}_3)_2\text{Pb}_2\text{Br}_7$ as the precursor. The particles prepared in a PMMA matrix increased their stability upon aging for at least 1 year compared with a few hours for the suspension in toluene.

Schmidt *et al.*⁶⁶ reported the preparation of colloidal hybrid perovskite NCs using a nontemplate strategy consisting of adding a mixture of a long-chain ammonium bromide, such as octylammonium bromide (OLABr) and methylammonium bromide (MABr), to an 80 °C solution of oleic acid in ODE, followed by the consecutive addition of PbBr_2 , and immediately afterward, the addition of acetone to induce the crystallization of the perovskite (yellow solid) with a PLQY of 20% in toluene. The electroluminescence (EL) of a thin-film light-emitting device prepared with these colloidal hybrid

perovskite NCs showed a noticeable improvement compared with that of bulk film, thus evidencing their potential for optoelectronic applications. A year later, it was demonstrated that more emissive and stable colloidal MAPbBr_3 NCs (PLQY of 83%) can be obtained in the absence of OA. ^1H NMR studies of the NCs, by reverting the perovskite back to its precursors in deuterated DMSO, combined with TGA, made it possible to determine the presence of OLABr (X₂ ligand) on the NC surface, as well as the composition of the nanomaterial (NC plus ligand).²⁵ The N 1s XPS spectrum of the NC showed only a band with maximum at 402.6 eV, thus corroborating the presence of alkylammonium to passivate the under-coordinated bromide of the NC surface. Then, bright lead bromide perovskite NCs (PLQY of about 100%) were prepared by following the LARP technique (see below), using the quasi-spherical-shaped 2-adamantylammonium bromide as the only capping ligand.³⁴¹ Though extraordinarily luminescent, these NCs showed a trend to aggregate due to the high interaction between the adamantyl moieties; in fact, they exhibited an average lifetime on the microsecond scale. The high affinity of the adamantyl moiety for the cavity of cucurbit[7]uril enabled the preparation of perovskite NCs with a host–guest complex as capping ligand, which showed a higher photostability under contact with water than the NC passivated with 2-adamantylammonium bromide.³⁴¹ Among various ligands, primary amine/carboxylic acid ligand pairs became the most commonly used pairs of organic ligands for the synthesis of bright colloidal perovskite NCs.^{14,141} The LARP strategy, introduced by Zhang *et al.*,²⁹ consisted of a dropwise addition of the capping ligands (octylamine and oleic acid) and the MAPbBr_3 perovskite precursor solutions into a low polar solvent, followed by centrifugation at room temperature to remove bulk material. The PLQY of MAPbBr_3 was high and well-preserved after purification (PLQY ~80%). Similarly, Protesescu *et al.* prepared highly luminescent and monodispersed colloidal CsPbBr_3 (PLQY of 90%) by a hot-injection methodology using oleylamine and oleic acid as organic ligands.¹⁴

Table 1 shows the chemical structure of the organic/inorganic ligands mentioned in this section, including acids, such as alkylcarboxylic, alkylphosphonic, alkylsulfonic and alkylphosphonic acids, alkylamines, alkylammonium salts, alkylthiols, and zwitterionic species. De Roo *et al.*⁸⁴ performed ^1H NMR spectroscopic studies to determine the eventual ligand(s) at the NC surface and also to gain insight into the surface chemistry of CsPbBr_3 NCs synthesized using oleylamine, oleic acid, a Cs-oleate solution, octadecene, and PbBr_2 . NOESY experiments demonstrated that octadecene and oleic acid did not bind to the NC surface, while oleylamine bromide was proposed as the capping ligand. It was suggested that the oleylamine cation might have bound to the surface bromide atoms *via* a hydrogen bridge and the bromide anion might have bound to cesium or lead atoms located on the surface, in agreement with the ionic character of the CsPbBr_3 NCs.³³⁷ However, the data were not conclusive as to whether the NCs were stabilized by oleylamine bromide or oleylamine oleate, both with a pair of X-type ligands, which corresponds to an $\text{NC}(\text{X})_2$ binding motif. Three possible combinations of these ligands were then proposed: oleylamine bromide, oleylamine oleate, and the unprotonated amine (L-type ligand). As a consequence of the fast exchange between the ligands, it was difficult to determine their individual contribution on the surface of the NCs. The

Table 1. Chemical Structure of Organic/Inorganic Ligands Used To Prepare Colloidal LHP NCs, Categorized According to the Functional Group and Covalent Bond Classification

Type of Ligands	Classification of the ligands by Functional group and chemical structure																														
X-type	<p>Alkylammonium salt</p>  <p>hexyl-, octyl- or dodecylammonium bromide</p>  <p>Didodecyldimethylammonium bromide</p> <p>Alkylcarboxylic acid</p>     <p>propionic acid oleic acid cinnamic acid 2,2'-iminodibenzoic acid</p> <p>Alkylthiols</p>  <p>octanethiol</p> <p>Alkylphosphonic acids</p>  <p>n= 1, 6, 8, 14, 18</p> <p>Alkylsulfonic acids</p>  <p>dodecylbenzene sulfonic acid</p> <p>Zwitterionic compounds</p>  <p>Sulfobetaine</p>  <p>N-hexadecylphosphocholine</p>  <p>gamma-aminobutyric acid</p>  <p>N,N-dimethyldodecylammonium butyrate</p>  <p>Lecithin R, R' = palmityl, stearyl, oleyl, linoyl, linolenyl</p>																														
L-type	<p>Alkylamine</p> <table border="1"> <thead> <tr> <th>Primary amine</th> <th>Bulky primary amine</th> <th>Secondary amine</th> </tr> </thead> <tbody> <tr> <td>Linear and small primary amine</td> <td>Bulky primary amine</td> <td>Dialkylamine</td> </tr> <tr> <td></td> <td></td> <td></td> </tr> <tr> <td>hexyl-, octyl- or dodecylamine</td> <td></td> <td>n = 1, 2, 3, 4, 7</td> </tr> <tr> <td></td> <td></td> <td></td> </tr> <tr> <td></td> <td></td> <td></td> </tr> <tr> <td></td> <td></td> <td></td> </tr> <tr> <td></td> <td>R = </td> <td></td> </tr> <tr> <td></td> <td></td> <td>PSS-[3-(2-aminoethyl)amino]propyl-heptaisobutyl substituted</td> </tr> </tbody> </table> <p>Alkylphosphine oxide</p>  <p>trioctylphosphine oxide</p>				Primary amine	Bulky primary amine	Secondary amine	Linear and small primary amine	Bulky primary amine	Dialkylamine				hexyl-, octyl- or dodecylamine		n = 1, 2, 3, 4, 7											R = 				PSS-[3-(2-aminoethyl)amino]propyl-heptaisobutyl substituted
Primary amine	Bulky primary amine	Secondary amine																													
Linear and small primary amine	Bulky primary amine	Dialkylamine																													
																															
hexyl-, octyl- or dodecylamine		n = 1, 2, 3, 4, 7																													
																															
																															
																															
	R = 																														
		PSS-[3-(2-aminoethyl)amino]propyl-heptaisobutyl substituted																													
Z-type	<p>K⁺ cation</p>																														

addition of small amounts of excess oleic acid and oleylamine before precipitation preserved the colloidal integrity and PL of the NCs. They corroborated the presence of a tightly bound fraction of oleic acid by means of NMR spectroscopy using dodecylamine/oleic acid as the ligand pair.

It was reasoned that oleic acid cannot bind by itself, but it binds as an ion pair with amine, the actual tightly bound ligand pair being oleylammonium oleate. Huang *et al.*³⁴² have suggested that oleylamine (i) acts as an L-type coordinating agent binding to Pb^{2+} to form a Pb^{2+} –oleylamine complex and (ii) reacts with oleic acid to form the oleylammonium oleate salt, and then oleate coordinates to Pb^{2+} due to the high coordination number of the metal cation (between 2 and 10).³⁴³ Consequently, the N 1s XPS spectrum showed two peaks, at 398.6 and 400 eV, which can be ascribed to the oleylamine and methylammonium/oleylammonium, respectively, while the O 1s XPS showed two peaks at 532.3 and 533.7 eV, which can be attributed to two non-equivalent oxygen atoms of carboxylic acid and to the two chemically equivalent oxygen atoms of oleate, respectively.

González-Carrero *et al.* combined a short primary amine and a short carboxylic acid, such as 2-adamantylamine and propanoic acid, as ligand pairs to produce highly photoluminescent (PLQY ~100%) colloidal $CH_3NH_3PbBr_3$ perovskites.³³⁰ The N 1s XPS spectrum deconvoluted into two peaks centered at 399.8 and 401.5 eV with an area ratio of 0.3; these peaks can be ascribed to 2-adamantylamine and the methylammonium salt, respectively. Both O 1s and C 1s XPS spectra confirmed the presence of carboxylic acid and carboxylate species. The quantification of the perovskite components by XPS showed an atomic ratio of 2.7 and 1.1 for Br/Pb and N/Pb, respectively. This can be considered as a presence of bromide vacancies (V_{Br}) in the perovskite more than an excess of lead atoms, as was observed by other researchers.¹⁹⁴ These LHP@capping nanomaterials showed a low tendency to aggregate in solution due to the reduction of the ligand–ligand interaction between the NCs while preserving the high QY. Those NCs assembled in solid films with thicknesses of hundreds of nanometers also retained a high PLQY, specifically ~80%.³³⁰

Primary amines with a branched structure have been used as an L-type ligand, leading to perovskites with a low PLQY. Examples of this type of ligands³⁴⁴ are (3-aminopropyl)-triethoxysilane (APTES) and polyhedral oligomeric silsesquioxane (POSS) PSS-[3-(2-aminoethyl)amino]-propylheptaisobutyl substituted, which have enabled a good control over the size of $CH_3NH_3PbBr_3$ NCs. Their low PLQY of <20% has been attributed to an inadequate passivation of the nanoparticle surface due to the steric effect of the branched ligands. In addition, $CH_3NH_3PbBr_3$ NCs have been passivated with a commercial cyclic peptide cyclo(RGDFK), containing five amino acids (arginine, glycine, aspartic acid, phenylalanine, and lysine).³⁴⁵ Modeling of $PbBr_3^-$ /cyclo(RGDFK) precursor complexes suggested the preferential coordination of the peptide to the $PbBr_3^-$ *via* the amine *versus* the guanidine group, which is consistent with the broadening of the $-NH_3^+$ moiety peak (3200 cm^{-1}) in the FTIR spectrum of the complex. The low PLQY (~20%) of the perovskite NCs passivated with cyclo(RGDFK) has been ascribed to charge transfer from the perovskite core to the peptide shell.

Secondary amines of different length, such as dihexyl-, dioctyl-, didecyl-, didodecyl-, and dioctadecylamine, have been used to prepare, in combination with oleic acid, $CsPbBr_3$

nanocubes with good emissive properties (48–80%) and a uniform cubic shape that allows their self-assembly in $50\text{-}\mu\text{m}$ -sized superlattices.¹⁴³ Interestingly, the pure-shaped NCs were obtained irrespectively of the length of the amine, oleic acid concentration and temperature. Density functional theory (DFT) calculations suggested that the binding of the dialkylammonium molecules to the [100] facets of $CsPbBr_3$ is weak and secondary to that of oleate; otherwise, it would cause a drastic distortion to the lattice.¹⁴³

Different capping agents, such as acids (oleic, phosphonic and sulfonic acids) and thiols, have been proposed to avoid the labile binding of amines (L-type ligand), ammonium/halide, and ammonium/oleate pairs (X₂-type ligands) to the NC surface. There is some controversy regarding the performance of oleic acid as the $CsPbX_3$ NC surface ligand. Yassitepe *et al.* developed an amine-free method to prepare $CsPbX_3$ NCs passivated by only oleic acid,³⁴⁶ which exhibits strong interaction with the surface, and as a result, the NCs can be washed several times. However, oleic acid does not seem to be a good candidate to provide $CsPbX_3$ NCs with a high PLQY. By contrast, Lu *et al.* built colloidal $CsPbBr_3$ with oleate as the only ligand (X-type ligand) and produced nanocubes of 11.2 nm with a PLQY of 70%. They showed a colloidal stability over at least 2 months, which is considerably higher than that reported for LHP@amine-oleate-passivated NCs.³⁴⁷ ¹H NMR spectroscopy corroborated oleate as the surface ligand, which was then effectively replaced by cinnamic acid derivatives, namely, *trans*-cinnamate and *trans*-3,5-difluorocinnamate, as demonstrated by FTIR spectra of the NCs (quantitative removal of the native oleate), as well as by ¹⁹F NMR and XPS measurements of the difluoro compound (observation of a broad signal and the presence of F signals, respectively). The easy replacement enabled the tuning of the NC optical/electronic properties but decreased its PLQY. Interestingly, LHP@cinnamate NCs showed enhanced photocatalytic activity for α -alkylation of aldehydes. The positive effects of the ligands in terms of the NC photocatalytic response might be due to (a) an increase of the NC photoredox potential, (b) a change in the ligand shell permeability, and (c) a good passivation of the surface defects, thus increasing the lifetime of the photocarriers and/or reducing surface catalytic sites.³⁴⁷ Another important factor can be the synergy between the NC surface and its organic ligand to lead to a high substrate preconcentration near the NC surface (for further details, see section “Photocatalysis Using Perovskite NCs”).³⁴⁸ More studies are required to determine the contribution of these factors on the performance of the NCs in photocatalysis.

The combination of trioctylphosphine and oleic acid has been used to prepare nanocubes of $CsPbBr_3$ NCs (PLQY of ~60%) with oleate as the only capping ligand; this synthetic route can be extended to *n*-tetradecylphosphonic acid and diisooctylphosphonic acid.³¹ ³¹P NMR spectroscopic studies were performed to determine the role of trioctylphosphine and oleic acid in $PbBr_2$ solubility; these studies indicate a competing interaction between the protic acid and $PbBr_2$ for the oxygen of TOPO. ¹H NMR studies give information on the dynamics of the Cs-oleate capping agent by focusing on the broadening and shift of the signals compared to those of the free acid. Negative cross-peaks in the NOESY spectrum corresponded to species with long correlation times with a movement that was slower in solution compared to small free molecules. A diffusion coefficient of $242\text{ }\mu\text{m}^2/\text{s}$, calculated by DOSY spectroscopy, was highly reduced compared to $725\text{ }\mu\text{m}^2/\text{s}$ in the free acid

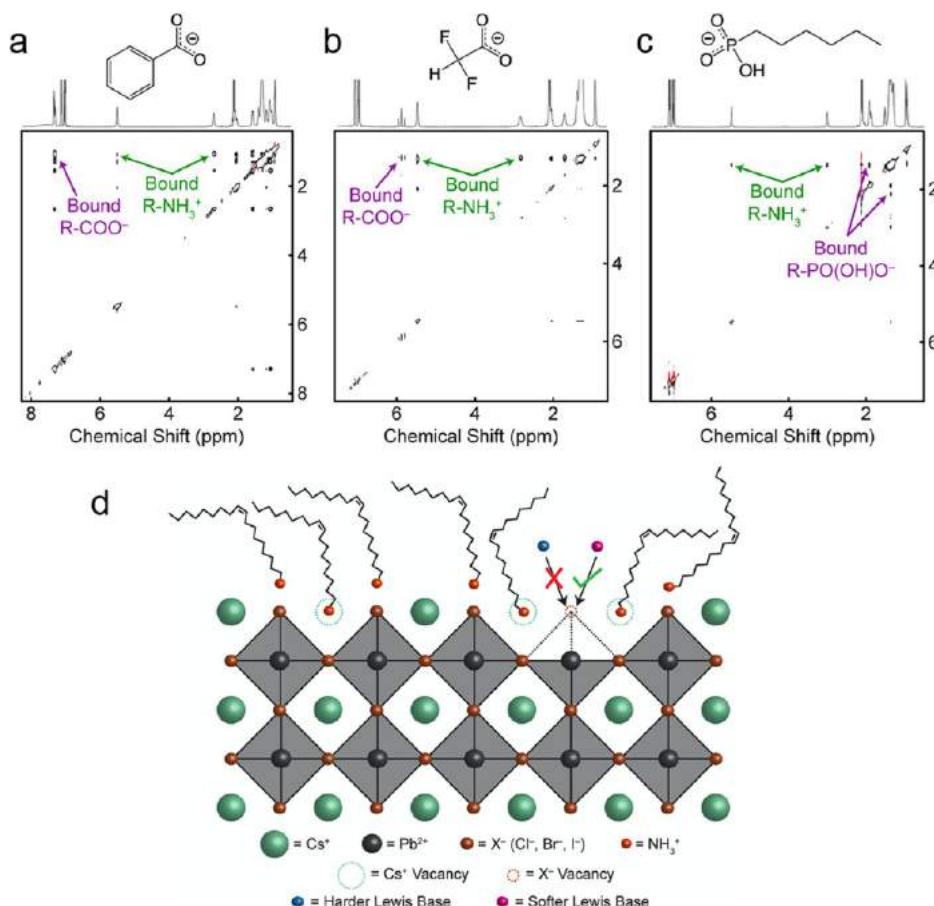


Figure 31. ^1H NOESY NMR spectra of CsPbBr_3 NC samples exchanged to ligand pairs of oleylammonium and (a) benzoate, (b) difluoroacetate, and (c) hexylphosphonate. All ligand pairs feature negative (black) NOE signals rather than positive (red) NOE signals, thereby corroborating their interaction with the NC surface. (d) Schematic representation of a cesium- and halide-deficient surface terminated by CsX facets, consistent with experimental results. Reproduced from ref 194. Copyright 2018 American Chemical Society.

and corresponded to a 76% of bound oleate species on the NC surface.¹⁷⁹

Sulfur-containing X-type ligands, alkylthiol and thiocyanates, were proposed to replace the oleylamine/oleic acid pair of ligands and to act as better passivation agents by reducing the surface defects and leading to NCs with a monoexponential PL lifetime and a better PLQY.³⁴⁹ A combination of alkylthiols with alkylamines or alkyl acids was used to control the crystal structure from orthorhombic CsPbBr_3 toward tetragonal CsPb_2Br_5 nanowires and nanosheets, which exhibited a high stability at high temperature and under humid conditions.

An exhaustive and systematic surface chemistry study was reported by Alivisatos *et al.* in 2018 to draw together the observations from several reports on this subject.¹⁹⁴ A methodology to obtain trap-free lead-halide NCs was proposed based on the combination of different techniques, such as NMR, NOESY and fluorescence spectroscopies, with *ab initio* calculations that evidenced that a soft X-type ligand can properly passivate the uncoordinated lead atoms, created by the halide vacancies on the NC surface. A cesium vacancy on the surface can be replaced by the oleyl ammonium cation. The lower the NC concentration (high dilution), the greater number of surface V_X , due to low binding of the oleyl ammonium halide pair. NMR line width was used to determine the number of trap states, related to V_X , which combined with the PLQY gave the ratio between the radiative and nonradiative rate constant (k_r/k_nr). The k_r/k_nr ratio value

was related to the defect tolerance of the different halide perovskites (9500, 390, and 53 for CsPbI_3 , CsPbBr_3 , and CsPbCl_3 , respectively). Soft Lewis bases that can substitute halide vacancies and coordinate to lead (which is a relatively soft Lewis acid) can be a neutral molecule such as a pyridine and thiophene or an anionic X-type ligand, such as alkylphosphonate, S^{2-} , benzoate, fluoroacetate, methanesulfonate, or trioctylphosphine. A ligand exchange strategy was used to introduce different alkyl carboxylates for the oleyl ammonium-R-COOH ligand pair, such as benzoate, fluoroacetate, and difluoroacetate. Nuclear Overhauser effect NMR spectroscopy was used to confirm the binding of the ligands to the NC surface supported by the negative cross peaks (Figure 31A,B). A good affinity of softer X-type ligands for the NC surface was also confirmed by the negative (black) NOE of oleyl ammonium hexylphosphonate (Figure 31C). These anionic ligands, X-type Lewis bases, could bind to cesium atoms on the surface, but this is not thermodynamically favorable,³⁵⁰ indicating they are binding to the surface lead atoms eliminating the V_X . By contrast, hard Lewis X-type ligands, such as alkylcarboxylates, carbonates, and nitrates are inefficient passivating ligands (Figure 31D).

Alkylphosphonates as the only organic ligand were initially introduced by Xuan *et al.*²⁷⁴ CsPbBr_3 NCs passivated with 1-tetradecylphosphonate were prepared at room temperature with good emissive properties (PLQY of 68%) and extraordinary water and thermal stability using 1-tetradecyl-

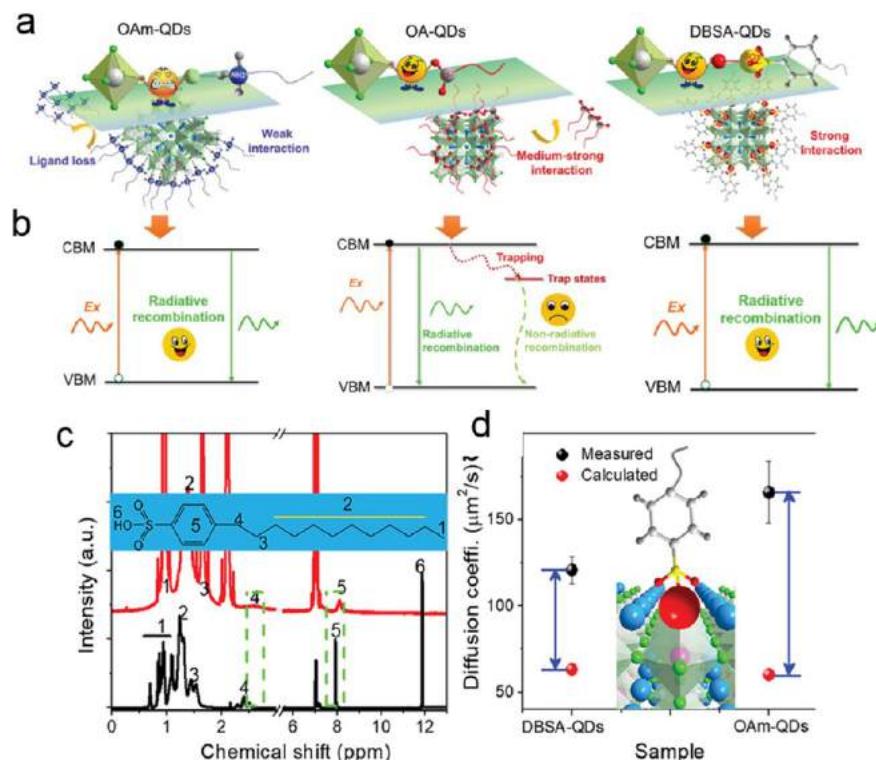


Figure 32. Comparison of different ligand strategies. (a) Binding motif on CsPbBr_3 QD surface and interaction strength of oleylammonium, oleic acid, and dodecylbenzenesulfonic acid (DBSA) ligands. (b) Effect of different ligands on exciton recombination dynamics. Evidence of strong DBSA–QD interaction. (c) ^1H NMR full spectra of pure DBSA and perovskite capped with DBSA after three purification cycles. (d) Diffusion coefficients of DBSA and perovskites capped with oleylammonium-capped NCs. Reproduced with permission from ref 352. Copyright 2019 John Wiley & Sons, Inc.

phosphonic acid. FTIR showed the replacement of the $\text{P}=\text{O}$ band at 1230 cm^{-1} , belonging to the 1-tetradecylphosphonic acid, by a broad band at $1000\text{--}900\text{ cm}^{-1}$, ascribed to $\text{Pb}=\text{O}-\text{P}$, thus corroborating the anchoring of the alkylphosphonate. Consequently, the O 1s XPS spectrum evidenced the presence of peaks at 530.8 and 530.2 eV corresponding to $\text{P}-\text{O}-\text{Pb}$ and $\text{P}-\text{O}$ bonds, respectively, confirming the FTIR analysis. Increasing the concentration of the phosphonic acid caused a blue shift in the absorption spectrum, which is consistent with the formation of smaller NCs due to a decrease in the rate of ligand release through the organic shell. The use of a phosphonic acid concentration higher than 7.5 mg mL^{-1} caused the decrease of NC PLQY, which can be associated with the steric hindrance resulting in a high number of uncoordinated surface atoms. Likewise, Zhang *et al.*³⁵¹ prepared colloidal CsPbBr_3 NCs by employing alkyl phosphonic acids as the only surfactant. NMR analysis revealed the presence of both phosphonic acid anhydride and hydrogen phosphonate species on the NCs surface. Theoretical calculations indicated a high affinity of phosphonate ligands for the NC surface and similar stabilization energy of the [001] and [110] facets, thus resulting in the formation of NCs with a truncated octahedron shape that exhibited a nearly 100% PLQY.³⁵¹ A follow-up of this work, by the same group reported the synthesis of CsPbBr_3 NCs using custom-made oleylphosphonic acid (OLPA). The lower temperature at which OLPA was soluble in the reaction mixture, compared to phosphonic acids with linear chains, allowed the synthesis of NCs (at $100\text{ }^\circ\text{C}$) with sizes down to 5 nm . These NCs were also more colloidal stable upon exposure to air than those of

ref 351, and again, this was traced back to the higher solubility of OLPA.

Alkylthiols were used to induce the transformation of CsPbBr_3 NCs to CsPb_2Br_5 nanostructures, and CsPb_2Br_5 nanosheets and nanowires were obtained by controlling the ratio between alkylthiols and alkylamine or alkyl acids.³⁴⁹ The presence of thiols in the system increased the tolerance to a high temperature and a high humidity environment favored by the good affinity of sulfur to lead atoms. The strong affinity of thiols for the Pb^{2+} sites reduced considerably the density of surface defects, leading to a PLQY close to unity and a monoexponential PL decay kinetics.

Long chain benzenesulfonic acid, such as dodecylbenzenesulfonic acid, was chosen as an excellent candidate to replace the bromide vacancy on the NC surface (Figure 32a).³⁵² In order to eliminate the defect energy levels, ligands with anionic heads with electronic features similar to those of bromide ions should be favorable. A good interaction of alkylsulfonic acid with lead is expected as the calculated binding energy of 1.64 eV in sulfonate- Pb is comparable with 1.47 eV in $\text{CH}_3\text{NH}_3\text{Br}-\text{Pb}$. The interaction strength between the ligand and the NC surface was estimated by diffusion-ordered spectroscopy (Figure 32d); the registered diffusion coefficient was smaller than for oleylamine-capped NCs, which is consistent with a stronger interaction between the sulfonate and the NC surface. Such ligand interacts with lead atoms and eliminates the defect energy level successfully, leading to CsPbBr_3 NCs with a PLQY higher than 90% . This binding was strong enough to resist a washing treatment, as shown by NMR (Figure 32c), keeping the PLQY up to 90% (Figure 32b). The high long-term colloidal stability and photostability under 400 nm irradiation

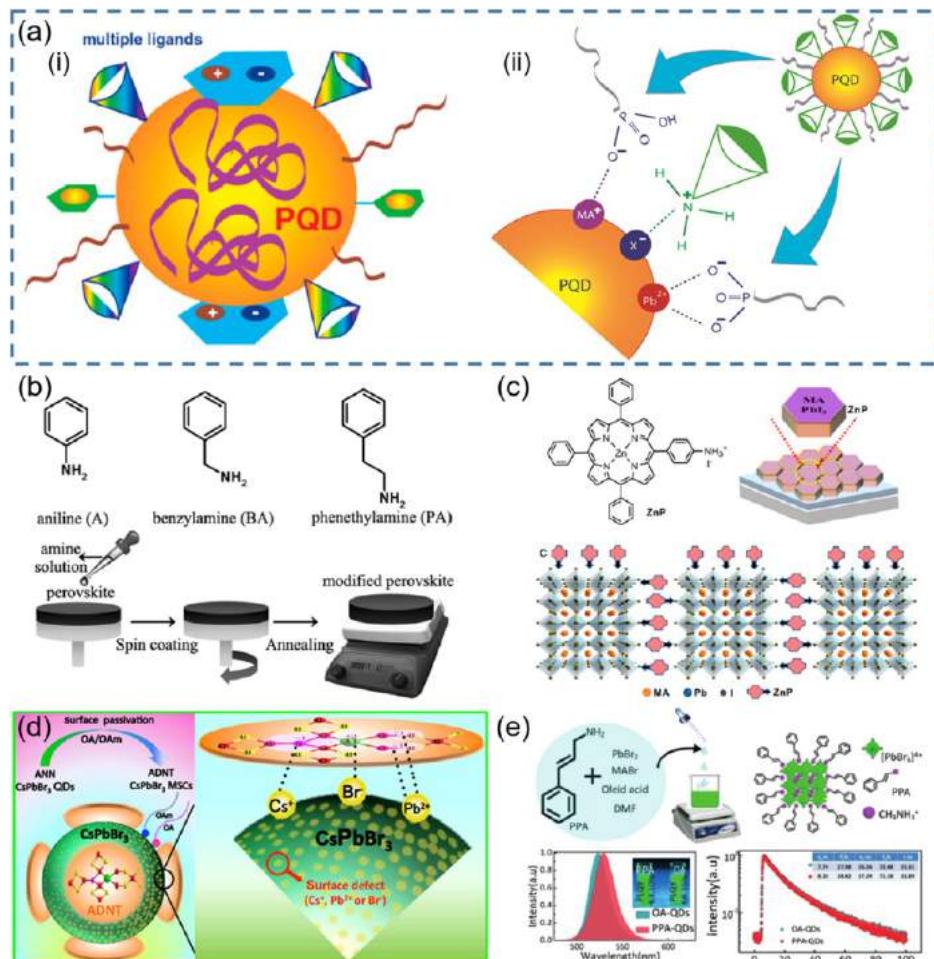


Figure 33. (a-i) Structural model for surface passivation of LHP NCs with multiple defects using a combination of ligands in a “cocktail” approach. Reproduced from ref 356. Copyright 2019 American Chemical Society. (a-ii) Schematic illustration of the major surface passivation mechanism of $\text{CH}_3\text{NH}_3\text{PbBr}_3$ perovskite NC surface defects. Reproduced with permission from ref 360. Copyright 2019 John Wiley & Sons, Inc. (b) Chemical structures of aniline, benzylamine, and phenethylamine, and schematic illustration of amine treatment of perovskite films through a spin-coating method, followed by an annealing process. Reproduced with permission from ref 359. Copyright 2016 John Wiley & Sons, Inc. (c) Structure of Zn-porphyrin (ZnP), scheme illustration of MAPbI_3 film with ZnP “doping”, and structure of perovskite encapsulated by ZnP. Reproduced from ref 367. Copyright 2019 American Chemical Society. (d) Schematic illustration of the major surface passivation mechanism of CsPbBr_3 magic-sized clusters or perovskite NCs surface defects. Reproduced from ref 368. Copyright 2019 American Chemical Society. (e) Illustration of the MAPbBr_3 NCs processing progress, the structural representation of PAA-perovskite NCs (PAA: 3-phenyl-2-propen-1-amine) in which PAA instead of OA (oleic acid) acts as capping ligands, steady-state PL spectra and representative photograph and PLQY values of PPA-perovskite NCs and OA-perovskite NC colloidal solution under 365 nm UV light, TRPL (time-resolved photoluminescence) spectra of PPA-perovskite NCs and OA-perovskite NC colloidal solution and color-tunable MAPbX_3 perovskite NCs with PPA as capping ligand. Reproduced with permission from ref 369. Copyright 2018 John Wiley & Sons, Inc.

of sulfonate-capped NCs compared to oleylammonium halide-capped NCs is a further evidence of the strong interaction between the sulfonate ligands and the NC surface, which makes these NCs appealing in thin-film technologies.³⁵²

Zwitterionic long-chain molecules, such as commercially available sulfobetaines, phosphocholines, and γ -amino acids, bind tightly to the CsPbBr_3 surface due to the fact that (i) they can coordinate simultaneously to the surface cations and anions on the NC surface and (ii) the cationic and anionic groups of their structure cannot be neutralized. The presence of the zwitterionic ligand as the sole ligand at the NC surface was evidenced by complete ionic dissolution of purified NCs in deuterated DMSO, which freed the surface-bound ligands.¹⁷¹ In addition, DOSY NMR spectroscopy of the NCs evidenced that the diffusion coefficient related to the broad resonances (corresponding to the zwitterionic ligands anchored to the NC

surface) was consistent with that estimated by the Stokes–Einstein equation (2 orders of magnitude slower than that of the free ligand). These NCs can be thoroughly purified, while preserving a PLQY above 90%, and can be densely packed in films, which exhibit high PLQY and good charge transport characteristics.

Inspired by these results, natural lecithin (a zwitterionic phospholipid with branched chains) was proposed as an effective ligand due to its branched chains that increase interparticle repulsion, thus enabling a high effective recovery of the NCs as well as single-nanoparticle spectroscopy when using diluted samples.¹⁷⁰ In addition to these X-type acid ligands, L-type ligands which possess lone electron pairs can also interact with lead ions with an unoccupied orbital.⁷⁷ However, from the synthesis viewpoint, it is difficult to introduce L-type ligands since many of them cannot dissolve

the precursors. Interestingly, Zhang *et al.*⁷⁷ prepared CsPbBr₃ NCs following the room-temperature antisolvent strategy, using only oleylamine (OLA) as the ligand. In this strategy, the polar solvent dissolves the precursors efficiently, thereby enabling the direct interaction of OLA with the NC surface; both theoretical and experimental results confirmed the significant passivation effect and strong binding energy of OLA. As a consequence, the NCs exhibited a PLQY close to unity and dramatically improved their stability when undergoing purification processes and in the presence of water.

To our knowledge, there are hardly any examples of surface passivation of lead-halide NCs with Z-type ligands; namely, the K⁺ cation and the K-oleate complex were used as passivating ligands. González-Carrero *et al.* prepared K⁺-capped CH₃NH₃PbBr₃ NCs by adding KPF₆ to the perovskite precursor dimethylformamide solution following the reprecipitation strategy.³³⁰ The K⁺ counterion is more lipophilic and less coordinating than bromide ions and replaced the excess of methylammonium cation at the NC surface. The NCs effectively self-assembled on a substrate to produce homogeneous solid films. On the contrary, Huang *et al.* added K-oleate to a toluene dispersion of previously prepared CsPbBr₃ NCs by following a hot-injection protocol; the post-synthetic treatment of the CsPbBr₃ NCs with K-oleate enhanced their photoluminescence and photostability.³⁵³

Interestingly, the high dynamic bonding between the NC surface and some capping ligands can be used advantageously to assemble perovskite NCs into two-dimensional superstructures. Zhang *et al.*³⁵⁴ have reported on the linear assembly of CsPbBr₃ NCs within PbSO₄-oleate polymers, resembling the morphology of a peapod. The capping pod mostly preserved the NC optical properties. In addition, González-Carrero *et al.*³⁵⁵ reported on the linear assembly of CH₃NH₃PbBr₃ NCs in lead(II) polymers by simply mixing the precursors of both the NC and the polymer. Correlative single-particle fluorescence and AFM evidenced the formation of ordered and nonconnected CH₃NH₃PbBr₃ NC-polymers, which were emissive and showed PL intermittency.

Simultaneous passivation of both cationic and anionic defects with anionic and cationic ligands is usually required for efficient stabilization of LHP NCs, and this essentially demands a “cocktail” approach, as illustrated in Figure 33a-i.³⁵⁶ The degree of acidity and basicity of the ligands is also important for effective passivation, as the defects can have a varying degree of acidity or basicity. Over the years, a wide range of organic acids and amines (e.g., oleylamine/oleic acid, octylamine, phosphonic acids (PAs), APTES, L-cysteine, aniline/benzylamine, phenethylamine, and *n*-trioctylphosphine (TOP) have been tested as ligands for LHP NCs.^{14,138,332,352,357–365} For instance, in the case of CsPbI₃, Cs⁺ is considered as a weak acid, Pb²⁺ a weak acid, as well, and I⁻ a weak base,³⁶⁶ while in the case of MAPbBr₃, MA⁺ is a weak acid and Br⁻ is a weak base (though stronger than I⁻).³⁶⁰ Based on the Pearson acid/base case concept, weak acid defects require weak base ligands, while weak base defects require weak acid ligand for optimal passivation.³⁶⁰ For example, short-chain organic PAs have stronger acidity, and thus their conjugate base has basicity stronger than that of their longer-chain counterparts.³⁶⁰ Four different linear alkyl PAs [PAs with the straight chain from short to long: MPA, *n*-hexylphosphonic acid, 1-tetradecylphosphonic acid (TDPA), and *n*-octadecylphosphonic acid (ODPA)] have been used in conjunction with APTES as capping ligands to synthesize

MAPbBr₃ perovskite NCs.³⁶⁰ As illustrated in Figure 33a-ii, the protonated APTES and deprotonated PAs produce weak acidic R-NH₃⁺, weak basic R-PO₂(OH)⁻, and even weaker basic R-PO₃²⁻. These ions likely passivate the surface weak basic Br⁻, weak acidic MA⁺, and even weaker acidic Pb²⁺ cations, respectively. In addition, MPA-APTES has larger acid–base equilibrium constant (K_{eq}) compared with that of HLA-APTES, TDPA-APTES, and ODPA-APTES, thereby producing of a higher concentration of R-NH₃⁺, R-PO₂(OH)⁻, and R-PO₃²⁻. Therefore, better passivation is achieved with the most acidic and shortest chain MPA.³⁶⁰ Similarly, a change in basicity of amines can also affect the passivation. As shown in Figure 33b, FAPbI₃ films have been prepared using amines with different basicity: aniline (pK_a 4.87), benzylamine (pK_a 9.34), and phenethylamine (pK_a 9.83). The basicity of these amines follows the order of phenethylamine > benzylamine > aniline; therefore, protonated phenylalkylamine should be the weakest acid, which should provide the most effective passivation by interacting with the weak base I⁻.³⁵⁹

If the acidity and basicity of both the acidic and basic ligands with the same anchoring groups are changed in the precursor solution during synthesis, the passivation outcome can also change. For instance, Pan *et al.*¹⁷⁷ systematically varied the hydrocarbon chain length of carboxylic acids and amines, from 18 carbons (18C) down to 2 carbons (2C), including carboxylic acids including C18A (OA), C12A (dodecanoic acid), C8A (octanoic acid), and C6A (hexanoic acid) and amines including C18B (OLA), C12B (dodecylamine), and C6B (hexylamine), to understand their effect on the surface properties of CsPbBr₃ PNCs. These organic surfactant molecules affect the nucleation and crystallization processes, with the C18A–C18B sample showing the highest PLQY indicative of the best passivation. This is attributed to the longer chain length C18A–C18B with larger K_{eq} , which produces higher concentrations of -COO⁻ and -NH₃⁺ ligands that are stronger bases and acids than that of the short-chain molecules to passivate Cs⁺, Pb²⁺, and Br⁻ defects.

The size and shape of molecular ligands can also strongly influence the effectiveness of passivation of MHPs, partly due to different steric hindrance, which in turn affects the morphology, crystalline phase, and optical and electronic properties of MHPs.³⁵⁶ On the other hand, MHPs of different sizes and shapes can create different combinations and types of defects and therefore demand molecular ligands with different sizes and shapes for optimal passivation. In addition to passivating the surface defects through the anchoring groups, the size and shape of the ligands are particularly important in stabilizing MHPs by preventing reaction with external environmental species such as O₂ and moisture.³⁴⁶ In particular, large ligands can afford multiple functional groups in one molecule. For example, butylphosphonic acid 4-ammonium chloride with a combination of phosphate and amino functional groups can simultaneously passivate MA⁺, Pb²⁺, and I⁻ defects.³⁷⁰ Additionally, suaraine, polyaniline, and quaternary ammonium salts have been shown to be good capping ligands for MAPbI₃ bulk, MAPbI₃ film, and MAPbBr₃ bulk, respectively.^{358,371} Peptides containing both -NH₃⁺- and -COO⁻- in one molecule have been used to passivate MA⁺, Pb²⁺, and Br⁻ of MAPbBr₃ perovskite NCs.³⁶³ Similarly, trifunctional L-cysteine has been used to passivate MAPbBr₃ perovskite NCs and induced self-assembly of perovskite NCs, based on synergistic effects among -NH₃⁺-, -COO⁻-, and -SH- groups.³⁵⁷ Therefore, the key choice of the size of

molecular ligands not only depends on the size and surface defects distribution of perovskites but also relates to the synergistic effects of the functional groups of the used ligands.

Regarding the ligand shape, this can be linear, branched, umbrella-shaped, planar, or spherical. Most studies to date have used linear-shaped molecules, such as OA and OLA as capping ligands.^{84,372} In addition, a few attempts were made with branched ligands. For instance, Zhu *et al.*³⁷³ used protonated (3-aminopropyl)trimethoxysilane (APTMS, umbrella-shaped) ligands in the synthesis of CsPbBr₃ perovskite NCs. The authors found that the resulting NCs exhibit improved PLQY and stability in polar solvents. Similarly, umbrella-shaped APTES and POSS PSS-(3-(2-aminoethyl)-amino)propyl heptaisobutyl-substituted (NH₂-POSS) have been used along with OA to passivate MAPbBr₃ perovskite NCs for enhanced stability.³⁴⁴ This is attributed to the strong steric hindrance and propensity for hydrolysis of APTMS, APTES, and NH₂-POSS, which prevent molecules such as H₂O and O₂ from reaching and reacting with the core of perovskites.

The combination of the umbrella-shaped APTES and linear OA does not appear to improve the stability of bulk MAPbI₃ films, an effect that can be attributed to the higher steric hindrance among APTES molecules.³⁷⁴ However, interestingly, linear OA alone is highly effective in passivating bulk films but not perovskite NCs. This is likely because the linear OAs can form a self-assembled monolayer on the bulk film surface, which is less likely for perovskite NCs due to their large curvature.³⁷⁴ For bulk MHP films, some planar and spherical molecular ligands also show good passivating ability. As shown in Figure 33c, when the planar molecular ligand of monoammonium ZnP is used as a molecular ligand for MAPbI₃ film, the interaction between NH₃⁺ and I⁻ leads to effective passivation.³⁶⁷ Another interesting planar molecular ligand is aluminium dihydroxide nitrate tetrahydrate (ADNT), along with OA and OLA, which was found to passivate the CsPbBr₃ surface very efficiently to the point that PMSCs were generated in addition to perovskite NCs (see the section below).³⁶⁸ This was attributed to the ADNT being planar on the surface of the PMSCs or perovskite NCs with its NO₃⁻ and OH⁻ groups binding to the Cs⁺ and Pb²⁺ defect sites and Al³⁺ binding to the Br⁻ defect sites of the PMSCs or perovskite NCs (Figure 33d). In addition, the spherical-shaped molecular ligand of mesostructured [6,6]-phenyl-C61-butyric acid methyl ester (ms-PCBM) has been used to passivate MAPbI₃ films owing to the hydrophobic and high-performance mesostructure of ms-PCBM.³⁷⁶ It would be interesting to test such ligands for perovskite NCs, as well.

Although long alkyl chain and alkoxy silanes molecular ligands are effective in passivating MHP NCs to improve their optical properties and stability, their insulating nature limits electronic coupling among MHP NCs and thereby impedes charge transfer and transport important for device application.^{335,369} One way to improve inter-NC coupling and charge transport is to use conjugated or conductive molecular ligands, such as aromatic, alkene, and alkyne compounds with an unhindered positive or negative terminal ion that will interact strongly with the surface defects.^{335,369} For instance, as shown in Figure 33e, the conjugated amine containing a C=C group of an aromatic molecule ligand 3-phenyl-2-propen-1-amine (PPA) has been used to prepare MAPbBr₃ NCs.³⁶⁹ Compared with OA, the carrier mobility of bulk PPA-MAPbBr₃ film increases almost 22 times over that of PA-

MAPbBr₃ films without compromising stability and optical properties. The conductivity of PPA-MAPbBr₃ perovskite NC films was improved due to enhanced coupling between perovskite NCs.³⁶⁹ Similarly, conjugated PPA with both “quasi-coplanar” rigid geometrical configuration and distinct electron delocalization characteristics has also been used to modify MAPbI₃ films. The conjugated cation coordinating to the surface of the perovskite grains/units provides a network for charge exchange.³⁷⁷ In addition, short conductive aromatic capping ligands such as benzylamine (BZA) and benzoic acid (BA) have also been used to synthesize MAPbBr₃ perovskite NCs with high PLQY (86%), indicative of a well-passivated surface. The perovskite NCs synthesized using BZA/BA capping ligands exhibit higher conductivity and longer charge carrier lifetime compared to those of MAPbBr₃ perovskite NCs with insulating OA and APTES capping ligands. This was attributed to the delocalization of the excitonic wave function of the perovskite NCs by the aromatic ligands.³³⁵

The valency or oxidation state of the ligand and the charge density and distribution in the ligand can critically affect how effective it can passivate the MHPs. For monovalent and divalent cationic surface defects, it would be ideal to use corresponding oppositely charged monovalent and divalent ligands for their passivation. With some weak acid ligands such as PAs, multiple conjugate bases with different valency or charges can be produced upon deprotonation, which can passivate differently charged cations, such as MA⁺, Cs⁺, or Pb²⁺ defects.³⁵⁶ Specifically, for the PA-APTES MAPbBr₃ perovskite NCs discussed earlier, APTES is protonated and can produce a charged functional groups of R-NH₃⁺ to passivate Br⁻. On the other hand, with the two proton transfers of R-PO₂(OH)⁻, PA can produce two charged functional groups of R-PO₂(OH)⁻ and R-PO₃²⁻ that could passivate MA⁺ and Pb²⁺, respectively.³⁶⁰ The above example is in contrast to OA-APTES MAPbBr₃ perovskite NCs that have two charged functional groups of R-NH₃⁺ and R-COO⁻, with the latter passivating both MA⁺ and Pb²⁺.³⁶⁰ Therefore, the valence state of the molecular ligands should ideally be consistent with the valence state of the surface defects for optimal passivation.

Passivation of Perovskite Magic-Sized Clusters. Perovskite magic-sized clusters (PMSCs) are ultrasmall (usually <2 nm) nanoparticles with a narrow size distribution and strong quantum confinement. Recently, it has been found that the ligands play a key role on the preparation and passivation of PMSCs, that is, clusters that have a single size or in any case an extremely narrow size distribution.^{368,375} Compared to perovskite NCs, PMSC are smaller and less stable and thereby they require better protection or passivation. As a result, strong ligands and high concentrations of ligands favor PMSCs over perovskite NCs.^{368,375} Because of their highly uniform size distribution and narrow optical bandwidth, PMSCs are attractive for studying fundamental issues and as potential building blocks for creating larger PNCs.³⁷⁸⁻³⁸⁰ It was found that one of the key factors in producing PMSCs is the amount of Lewis acid ligands used, with more acids leading to more PMSCs.³⁶⁸ However, not all the type of Lewis acids can produce pure PMSCs, and the PMSCs only exist in organic solvent owing to their small size (< 2 nm).³⁶⁸

To date, there have been a few reports on PMSCs and their ensembles. Single sized (~2–4 nm) APbX₃ (where A = CH₃NH₃⁺ or Cs⁺) nanocrystalline phosphors have been synthesized using OA and OLA as capping ligands, showing a high PLQY (~80%).³⁸¹ CsPbBr₃ nanoclusters with ~2 nm

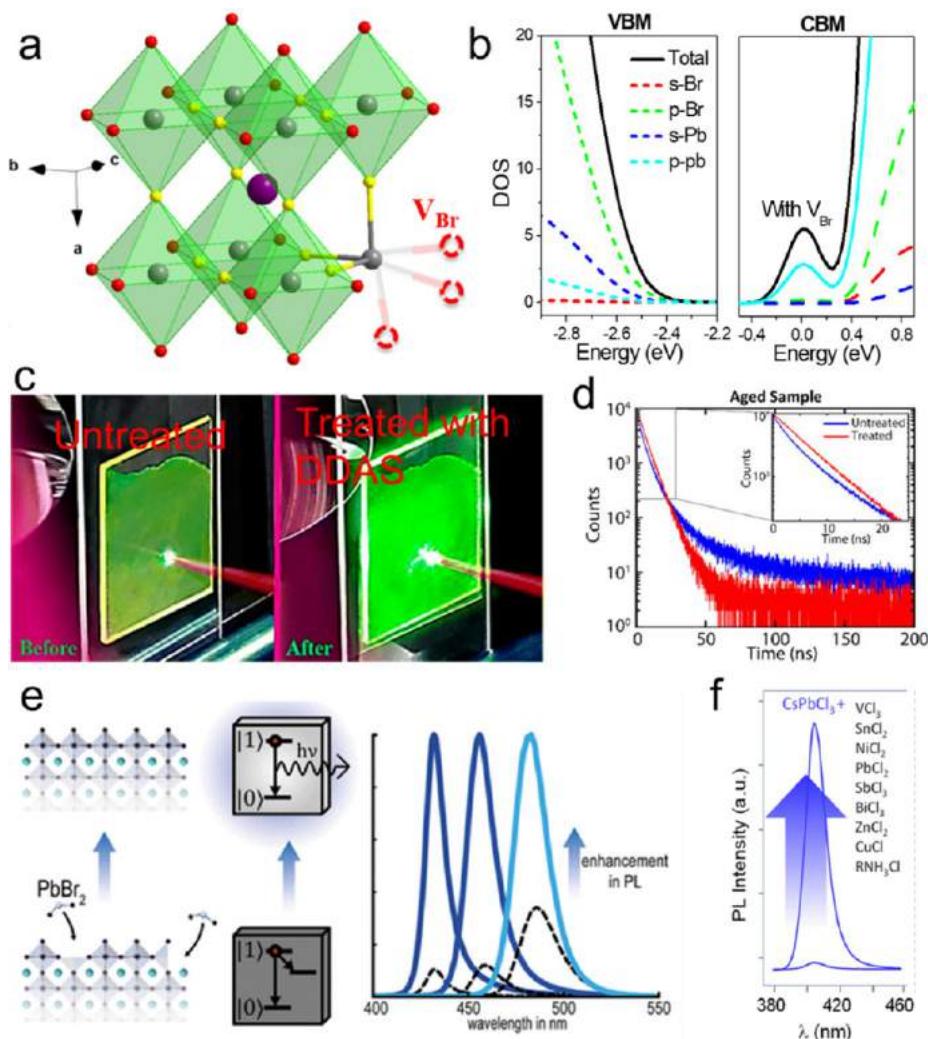


Figure 34. (a) Crystal structure of CsPbBr₃ NC, with the presence of a surface V_{Br}. Reproduced with permission from ref 392. Copyright 2019 John Wiley & Sons, Inc. (b) Electronic density of states (DOS) curves of valence band maximum and conduction band minimum of CsPbBr₃ with V_{Br}. Reproduced with permission from ref 352. Copyright 2019 John Wiley & Sons, Inc. (c) CsPbBr₃ NC films before and after being treated with DDAS. Reproduced from ref 389. Copyright 2015 American Chemical Society (d) PL decay of treated and untreated CsPbBr₃ NC with NH₄SCN. Reproduced from ref 88. Copyright 2017 American Chemical Society. (e) CsPbBr₃ NPLs with post-treatment of PbBr₂. Reprinted with permission under a Common Creative Attribution 4.0 International license from ref 60. Copyright 2018 American Chemical Society. (f) Greatly improved PL of CsPbCl₃ NCs after being treated with metal chlorides. Reproduced from ref 87. Copyright 2018 American Chemical Society.

size and a sharp absorption peak at ~ 398 nm have been synthesized using OA and OLA as capping ligands and converted into highly deep blue-emitting nanoribbons.³⁸² In addition, smaller size clusters (~ 0.6 nm) of CsPbBr₃ (nearly equal to the CsPbBr₃ unit cell length of 0.59 nm) have been synthesized using OA and OLA ligands.³¹⁶ Zhang *et al.* found that the single size of MAPbBr₃ and CsPbBr₃ PMSCs are strongly dependent on the ligands used.^{368,375} As shown in Figure 33d, a distinctive inorganic capping ligand based on a trivalent metal hydrated nitrate coordination complex, Al-(NO₃)₃·9H₂O, together with OA and OLA, has been used to control the synthesis of CsPbBr₃ PMSCs and CsPbBr₃ perovskite NCs. By changing the amount of metal complex ligand used, the final product can be tuned from perovskite NCs to PMSCs or to a mixture of both NCs and PMSCs, with excess ligands favoring PMSCs.³⁶⁸ The conversion from CsPbBr₃ perovskite NCs to PMSCs is mainly related to the concentration of trivalent metal hydrated nitrate coordination

complexes (TMHNCCs). The concentration of (TMHNCCs) affects the excitonic absorption of the CsPbBr₃ PMSCs ($\lambda = 430$ –441 nm) and CsPbBr₃ perovskite NCs ($\lambda = 447$ –518 nm), with more TMHNCC favoring CsPbBr₃ PMSCs over perovskite NCs.³⁶⁸ Due to the ultrasmall size and extremely large surface to volume ratio of PMSCs, a higher concentration of molecular ligands are necessary compared to perovskite NCs.

Strategies to Gain Insights into the Ligand–Surface Interactions. Pan *et al.*¹⁷⁷ have studied how to gain information on the ligand–surface interaction in CsPbBr₃ NCs from their purification step. The as-synthesized NCs were purified using hexane and a hexane/acetone mixture. NMR and FTIR measurements demonstrated that ammonium ligands can be preferentially removed from the NC surface compared to carboxylate; this is consistent with the weaker strength of the H-bonding interaction of alkylammonium with the surface bromide atoms [Br \cdots H–N $^+$] compared to the

lead–carboxylate coordination. The treatment of the NCs with a polar solvent destabilizes the hydrogen bond interaction producing a detachment of the ammonium from the NC surface, as was evidenced by the decrease and disappearance of the N–H bending vibration band in the FTIR spectrum (1575 cm^{-1}), while alkene protons (5.50 ppm) from oleate remained unchanged. Solvent-dependent ligand–surface interactions were clearly demonstrated, and this finding should be considered when ligands and washing solvents are used in the synthesis and purification steps.

A washing treatment with an antisolvent reduces the colloidal stability of the NCs due to a decrease of the ligand density on the NC surface. The addition of didodecyldimethylammonium bromide (DDABr), a branched ligand, can promote the exchange of the pristine ligands (oleylamine and oleic acid) on the NC surface with DDABr, thereby enhancing their photostability. However, this strategy has not proved successful enough in protecting the NC surface, as the obtained NCs deteriorated unavoidably after the washing step. The unwashed NCs were then sealed into a resin to fabricate a blue LED, which exhibited a higher photostability than that prepared with pure NCs.³⁸³ We recommend to read subsection *Isolation and Purification of Colloidal MHP Nanocubes*, for specific examples on metal-halide perovskite nanocubes.

In addition, post-synthesis ligand exchange allows one to estimate the binding constant of the added ligands to get thermodynamically stable coordination of organic ligands to the NC surface. Thus, two different surface CsPbBr_3 NCs were prepared using the hot-injection method: (i) NC terminated with oleyl ammonium bromide (PLQY of 92%) and (ii) NC terminated with Cs-oleate species (PLQY of 69%).³⁸⁴ Interestingly, the reduction of scattering was associated with the saturation of the NC binding energy. It has been demonstrated that primary alkyl ammonium and benzylammonium bromides bind to the NC surface with a binding constant $>10^5\text{ M}^{-1}$, but the constant is reduced to 10^4 M^{-1} with short length ligands, sterically hindered ligands (e.g., triethylammonium and oleyl ammonium), and weak acid ligands (such as phenylammonium). The higher the binding constant of the ligands to the NC surface, the better the long-term stability and emissive properties due to a complete surface passivation. However, the excess of ammonium ligands could transform the core of the NCs by substitution of cesium and reconstruction of the NCs inducing a blue shift in the emission.

Post-synthetic treatment of CsPbI_3 NCs with a dicarboxylic acid, namely, 2,2'-iminodibenzoinic acid, enhanced their PLQY from 80 to 95%. NMR, XPS, and FTIR measurements confirmed the bidentate binding of the ligand by the carboxylic groups. DFT calculations are consistent with the anchoring of the bifunctional ligand to two lead atoms at the NC surface with a binding energy of 1.4 eV, compared to a binding energy of 1.14 eV for oleic acid. The dicarboxylic ligand stabilizes the NC surface, with low structural distortion and phase transformation, leading to high PLQY.¹⁷²

Post-synthetic Passivation of CsPbBr_3 NCs. The performance of LHP@capping NCs by following a post-treatment of the NCs has focused on all-inorganic CsPbX_3 . Defect energy levels result from the crystal discontinuity on the surface, and the role of passivation is mainly to reduce (ideally eliminate) the resulting surface defects. It is widely acknowledged that surface cesium atoms of CsPbX_3 NCs are replaced with protonated amine ligands, which interact with halide

atoms through hydrogen bonding (Figure 34a).^{17,350,385} Since only the orbitals of Pb and X atoms contribute to the band-edge, exciton recombination seems to take place primarily within the Pb–X octahedrons. The symmetric crystal structure makes lead vacancy (V_{Pb}) hardly affect the exciton recombination while V_X considerably influences the recombination process (Figure 34b).^{357,386,387} Therefore, the main purpose of both the post- and *in situ* passivation strategies is to fill the V_X on the surface. Furthermore, if the ligands possess physicochemical properties similar to those of halide ions, they can passivate the V_X directly. Pan *et al.* initiated the post-treatment of perovskite NCs in late 2015.³⁸⁸ CsPbBr_3 NCs were first treated with oleic acid and then with didodecyl dimethylammonium bromide (DDAB) or DDAS (here S means S^{2-} ; Figure 34c).^{177,389} The treatment significantly improved the PLQY and the stability of the CsPbBr_3 NCs and enabled stable stimulated emission from the NCs after 1.2×10^8 laser shots. The pretreatment of the NCs with oleic acid before the adsorption of DDAB is an indication of the complexity of the ligand–NC interaction. After that, Alivisatos' group treated CsPbBr_3 NCs with thiocyanate salts (NH_4SCN , NaSCN) and NH_4Br ³⁸⁸ by adding the salt powder into the NC dispersion directly and stirring the mixture at room temperature. They reported a PLQY value close to unity, with an obvious monoexponential PL decay (Figure 34d). The key point of this method is repairing a lead-rich surface (surface with V_X) with pseudohalogen ions by post-treating CsPbBr_3 NCs with bromides or related chemicals. For example, tetrafluoroborate salts, ZnX_2 , and PbBr_2 were used as the post-treating agents to improve the PLQY of green CsPbBr_3 NCs^{195,357,390} to close to 100%. In addition to these inorganic salts, organic salts with bromides were also applied to repair the surface V_{Br} to provide NCs with a PLQY of 100%.¹⁶¹ Such ligands endow CsPbBr_3 NCs with strong endurance against polar solvent washing and ambient storage, indicating their better potentials in future optoelectronic devices. The post-treatment of blue-emitting perovskite NCs is generally difficult. There are mainly two types of three-dimensional, blue LHPs: mixed-halide perovskites and CsPbBr_3 nanoplatelets. It is difficult to accurately passivate surface V_X of mixed halides since ion exchange occurs easily,⁵⁵ and it is challenging to ensure the stability of the emission wavelength during the surface treatment. For CsPbBr_3 NPLs, poor stability is the main obstacle during post-passivation.²³⁵ In spite of these difficulties, some interesting studies have been reported. For instance, the treatment of CsPbBr_3 NPLs of different thicknesses with a PbBr_2 –ligand solution led to an overall enhancement of their low PLQY (Figure 34e).⁶⁰ Considering NCs with a shorter emission wavelength, such as CsPbCl_3 NCs, Pradhan's and others' groups conducted comprehensive experiments and demonstrated giant PL enhancement when CsPbCl_3 NCs were treated with various types of metal chlorides (Figure 34f).^{87,148,391} It should be noted that no doping was detected. Considering the similarity of these inorganic salts, there is no doubt that the passivation of Cl vacancies on NC surface contributes greatly to the enhanced PLQY.^{86,101}

Post-synthesis Passivation versus *In Situ* Passivation of LHP NCs. The post-passivation strategy is a widely accepted strategy in the field of common semiconductor and perovskite NCs. However, additional impurities are unavoidable in such strategy and this might be detrimental for their optoelectronic properties. Further purification is often necessary to remove

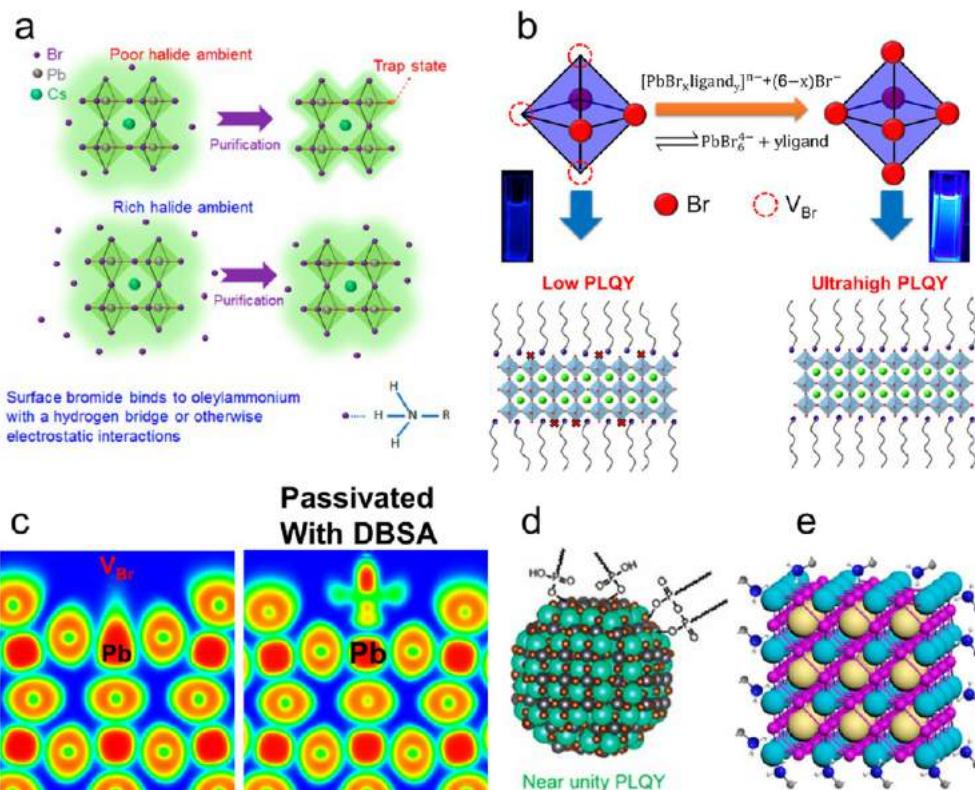


Figure 35. (a) Schematics for conventional and *in situ* passivation under halide-rich conditions with inorganic ammonium bromides. Reproduced from ref 321. Copyright 2017 American Chemical Society. (b) Schematic for ionic-equilibrium-based *in situ* passivation strategy for highly efficient CsPbBr_3 NPLs. Reproduced from ref 398. Copyright 2018 American Chemical Society. Direct *in situ* passivation with (c) X-type DBSA. Reprinted with permissions from ref 352. Copyright 2019 John Wiley & Sons, Inc. (d) X-type alkyl phosphonic acids and (e) L-type oleylamine. Panels d is reprinted from ref 351. Copyright 2019 American Chemical Society. Panels e is reprinted from ref 77. Copyright 2019 American Chemical Society.

the unreacted chemicals, which is challenging for perovskite NCs. Eliminating the surface defects during synthesis, *i.e.*, *in situ* passivation, *via* surface stoichiometric control, ligand design, and precursor engineering may be more favorable as no further treatment and purification steps are needed.^{327,393–395} As mentioned above, the main purpose of perovskite NC passivation is to compensate the halide vacancies (V_X) on the surface. According to this principle, Liu *et al.* added ammonium halide in the precursors to construct halide-rich NCs (Figure 35a).³²¹ During and after growth, the excess halide ions in the solution can fill the surface vacancy efficiently, contributing to reduce the nonradiative process and consequently enhancing the NC PLQY. This strategy was further modified by several other groups using metal bromides (ZnBr_2 , MnBr_2 , PbBr_2 , among others)^{332,396,397} to passivate the surface defects and consequently a PLQY close to unity was achieved. Although these metal bromides were added together with the precursors, no NC doping was observed.

LEDs fabricated with these NCs exhibited a record EQE value of 16.8%, indicating the superiority of the *in situ* passivation strategy; further studies are needed to gain insight into how these metal bromides work. By contrast, the addition of NiCl_2 during the preparation of CsPbCl_3 NCs resulted in NC Ni doping as well as a decrease in the surface chloride vacancy density,³⁹⁹ thus leading to NCs with a PLQY close to 100%. Therefore, more investigations are needed to identify the significance of the halide salts during synthesis.

Very recently, Yang *et al.* prepared highly efficient and stable $\text{CsPbBr}_x\text{I}_{3-x}$ NCs with emission wavelength at the pure red

region (637 nm) through the addition of potassium-oleate.⁴⁰⁰ Potassium bromide was detected on the surface, which passivated the V_X and inhibited the halide segregation simultaneously. The final LED exhibited high EQE and especially stable emission peak. Usually, the addition of inorganic halides also introduces impurities to some extent. Then, Wu *et al.* developed an *in situ* passivation strategy with organic halides (oleylammonium bromide) obtaining a record PLQY of 96% for CsPbBr_3 nanoplatelets emitting in the blue (Figure 35b).³⁹⁸ According to their approach, PbBr_6^{4-} complexes could be formed before nucleation of the NCs by controlling the amount of HBr. The formation of single-layered hybrid perovskites capped with oleylammmonium bromide after injection of PbBr_2 precursor was followed by the disconnection between PbBr_2 and ligands after the addition of HBr, thus shifting the ionic equilibrium toward the formation of isolated PbBr_6^{4-} octahedral complexes, due to the increased Br^- concentration. The process was monitored by absorption spectroscopy. LEDs based on these NPLs exhibited an ultranarrow electroluminescence emission with a full width at high maximum of 12 nm.

Direct *in situ* passivation was carried out with organic ligands of different natures and presenting strong affinity to Pb^{2+} ions: (i) X-type ligands, such as dodecylbenzenesulfonic acid³⁵² and alkylphosphonic,³⁵¹ and (ii) L-type ligand, such as oleylamine.⁷⁷ The groups of Zhang and Pradhan prepared CsPbX_3 NCs with ultrahigh PLQY by adding organic halides with long chains.^{78,401,402} Moreover, organic halides with multi-alkyl chains can participate in the *in situ* passivation of the NCs, but

they are not detected on the surface due to their large steric hindrance.³⁹² These organic halides play a role during the growth stage by enabling the formation of complete Pb–Br octahedrons and therefore a low surface V_X density. The surface is eventually capped by other long-chain ligands, such as oleic acid or oleylamine. This method provides more possibilities for tuning optical and structural features. The above-discussed *in situ* passivation methods were all based on the consideration of filling surface V_X . In a sense, if the ligands can passivate the exposed lead atoms directly, we would achieve efficient perovskite NCs using simply one kind of ligand.

On the whole, since most of the results confirmed that surface V_X is at the origin of carrier trapping and nonradiative recombination,^{194,392,399} the passivation strategy design for trap-free perovskite NCs should focus on the elimination of surface V_X . In fact, researchers have been succeeding in doing this and PLQY close to 100% have been achieved for almost all the visible emission wavelengths.

Summary and Future Prospects for Surface Chemistry and Passivation of MHP NCs. Perovskite QDs relevant for optoelectronic devices require not only capping ligands that stabilize NCs and enhance their luminescence, but also that promote charge injection and transport at the interface. Long-chain saturated amines and carboxylic acids, such as oleylamine and oleic acid, have been commonly used as passivating ligands of perovskite NCs surface to enhance their stability and optical properties. However, their insulating nature creates an electronic energy barrier and impedes interparticle electronic coupling, thereby limiting the application of the NCs in optoelectronic devices. Thereby, different strategies have been tested to overcome this issue. Control of the surface ligand density on the NC surface has been devised as a way to improve the stability and PLQY, as well as the uniformity and carrier-injection efficiency of perovskite thin films, and it has been attained *via* treatment with a mixture of polar/nonpolar solvents.¹⁸⁴

Shorter-chain saturated amines and acids have been used to enhance the performance of light-emitting diodes, such as those based on colloidal FAPbBr_3 NCs capped with *n*-butylamine⁴⁰³ and $\text{CsPbBr}_3/\text{CH}_3\text{NH}_3\text{Br}$ quasi-core/shell structures⁴⁰⁴ to provide green LEDs with EQE of up to 2.05 and 20.3%, respectively. Moreover, CsPbI_3 NC LEDs with EQE of 12.6% have been fabricated using octylphosphonic acid.⁴⁰⁵ In addition, relatively short-chain quaternary ammonium bromide salts, such as didodecyldimethylammonium bromide and didecyldimethylammonium bromide, has enabled the preparation of LEDs based on CsPbBr_3 NCs with an EQE of 9.71%.⁴⁰⁶ Interestingly, long-chain ligands, such as 3-(*N,N*-dimethyloctadecylammonio)propanesulfonate, capable of coordinating simultaneously to the cation and anion of CsPbBr_3 NC surface, have led to densely packed NC films in which the charge transport is not severely impeded.¹⁷¹

Ligand shortening combined with conductive capabilities has proved to be a promising strategy to facilitate charge transport between perovskite NCs by lowering the energy barrier.³³⁵ The passivation of MAPbBr_3 QDs with benzylamine and benzoic acid enhances the conductivity and carrier lifetime as well as the charge extraction efficiency, while preserving the high chemical stability and PLQY of the perovskite. In this regard, Yan *et al.* have recently proposed the use 3,4-ethylenedioxythiophene to passivate CsPbBr_3 NCs to provide photodetectors with enhanced performance by exploiting the

ligand capacity to be polymerized on the NC surface under the photocurrent of the photodetector, thus enhancing the device performance in up to 178% while exhibiting high stability in air.⁴⁰⁷ This molecular engineering strategy can be of great interest for the development of high-performance and stable optoelectronic devices based on perovskite NCs. Somewhat related, Hassan *et al.*⁴⁰⁸ have shown the beneficial effect of multidentate ligands to passivate effectively perovskite NCs, thus preventing halide segregation in I/Br mixed-halide perovskite LEDs under electroluminescent operation. Moreover, Han *et al.*⁴⁰⁹ have recently applied the Lewis base cyclam (1,4,8,11-tetraazacyclotetradecane) as an effective, self-sufficient passivation, multichelating ligand of perovskite NCs, thus boosting the performance of light-emitting diodes (external quantum efficiency (EQE) of 16.24%). These results are encouraging and give clues on the nature of the ligands needed to enhance the charge injection and transport at the interface of the passivated perovskite surfaces. Identifying ideal ligands which enable even more efficient optoelectronic devices, which combine enhanced chemical stability and high efficiency in charge injection and transport at the interface, requires further experimental investigations, as well as state-of-art theoretical calculations on surface chemistry.

Future development of passivation strategies should take into consideration electrical and optical properties, colloidal stability, and operation stability, simultaneously.¹⁷⁰ However, achieving these advantages together cannot be more challenging, and mixed passivation strategies with both organic and inorganic chemicals may be a better solution. Moreover, additional *in situ* passivation ligand systems are urgently needed to further promote the optoelectronic properties and stabilities.

OD NON-PEROVSKITE (PEROVSKITE DERIVATIVE) NCs

The 2016–2017 reports^{410–413} on so-called “zero-dimensional” (0D) Cs_4PbX_6 (X = Cl, Br, or I) materials and NCs inspired many research works on the synthesis and device applications of Cs_4PbX_6 colloidal nanocrystals.⁴¹⁴ Compared to their CsPbX_3 counterparts (also referred to as 3D perovskites), Cs_4PbX_6 NCs were shown to have improved thermal and optical stability, especially with respect to their high PLQY of green emission in the solid state. From a crystal structure point of view, 0D Cs_4PbX_6 exhibit isolated $[\text{PbX}_6]^{4-}$ octahedral units—in contrast to the corner-sharing $[\text{PbX}_6]^{4-}$ octahedra of 3D CsPbX_3 —surrounded by Cs^+ cations that are completely decoupled in all directions. The reduction of dimensionality from 3D to a strongly quantum-confined 0D gives rise to the molecular-like electronic properties of Cs_4PbX_6 , such as a widened band gap and an increased exciton binding energy, a reduced charge carrier mobility, and a lower conductivity. Meanwhile, it brings several interesting photophysical features into play, like small polaron absorption and broad-band ultraviolet (UV) emissions. In the following, we will review the recent work on the 0D perovskite NCs, particularly Cs_4PbBr_6 , by covering their syntheses and phase transformations, optical properties and molecular features, the origin of green emission, and optoelectronic applications.

Synthesis and Phase Transformation of Cs_4PbBr_6 NCs. Hot-injection and low-temperature reverse micro-emulsion methods are two popular methods to obtain highly monodisperse Cs_4PbX_6 NCs. The former method is also best known for synthesizing highly luminescent CsPbX_3 NCs, as shown by Protesescu *et al.*¹⁴ In their developed method, the

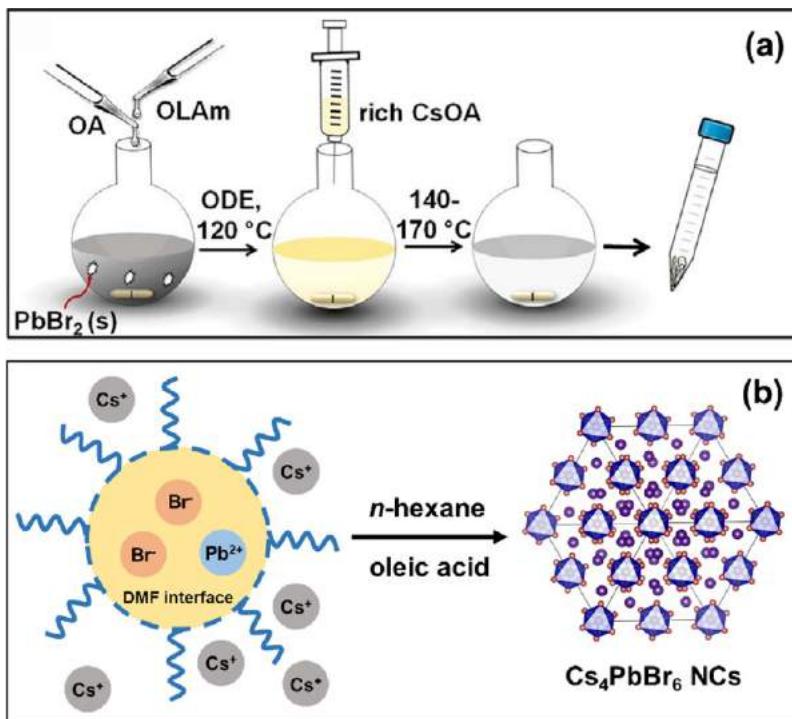


Figure 36. (a) Schematic illustration of the hot-injection method of synthesizing Cs_4PbBr_6 NCs in a rich Cs-oleate environment. Reproduced with permission from ref 415. Copyright 2019 Elsevier. (b) Schematic illustration of the low-temperature reverse microemulsion method of synthesizing Cs_4PbBr_6 NCs formed at the interface between an “oil” phase (*n*-hexane) and an “aqueous” phase (DMF). Redrawn from ref 413. Copyright 2017 American Chemical Society.

precursor PbBr_2 was first dissolved in a nonpolar solvent with a combination of oleic acid and oleylamine and then Cs-oleate complex was injected (Figure 36a). Based on this, Akkerman *et al.* utilized a similar hot-injection strategy, but under Cs-rich conditions, to obtain nearly monodisperse Cs_4PbX_6 NCs with the size distribution of 10–36 nm.⁴¹¹ After that, Udayabhaskararao *et al.* developed another hot-injection method by mediating the excess ligands, and they found that the size of Cs_4PbX_6 NCs can be tuned by controlling the ratio of OA/OLA and also by the temperature.⁴¹⁶ Meanwhile, Zhang *et al.* reported the synthesis of Cs_4PbBr_6 NCs (size distribution: 26 \pm 4 nm) using a low-temperature reverse microemulsion method.⁴¹³ As illustrated in Figure 36b, the precursors PbBr_2 and Cs-oleate were first dissolved in DMF and hexane, respectively. These two solvents are immiscible, and thus, the NC nucleation rate was controlled by the slow release of Cs^+ ions from the Cs-oleate complex when the solvents were mixed. The microemulsion method has been used to obtain other inorganic perovskite NCs with different dimensionalities (CsPbBr_3 and CsPb_2Br_5),¹³⁵⁰ as well as the ligand-free highly emissive Cs_4PbBr_6 NCs.⁴¹⁸ Recently, Hui *et al.* reported a one-step method for the synthesis of Cs_4PbBr_6 NCs by mixing three independent precursors of Cs, Pb, and Br in a cuvette.⁴¹⁹ They proposed a two-step pathway for forming Cs_4PbBr_6 NCs. First, Pb and Br precursors immediately react to form intermediates (*i.e.*, $[\text{PbBr}_4]^{2-}$, $[\text{PbBr}_3]^-$, and $[\text{PbBr}_6]^{4-}$), and then the Cs precursor (CsOA) induces the assembly of the intermediates into Cs_4PbBr_6 NCs.

In addition to the direct synthesis methods mentioned above, Cs_4PbBr_6 NCs can be obtained *via* the phase transformation from CsPbBr_3 to Cs_4PbBr_6 NCs by adding different amines (Figure 37a). For example, Liu *et al.* showed that after adding OLA into the solution of CsPbBr_3 NCs, the

absorption around 492 nm from CsPbBr_3 NCs decreased while the absorption around 313 nm from Cs_4PbBr_6 NCs increased (Figure 37b).⁴²¹ The evolution of the normalized absorbance at these two spectral positions had the inverse dependence on the OLA concentration. They found that including large amounts of 1,3-propanedithiol (PDT) had almost no effect on the absorption spectrum without adding OLA, indicating that the PDT cannot trigger the transformation. Therefore, such transformation was triggered by adding oleylamine and the size uniformity and chemical stability of the Cs_4PbBr_6 NCs can be improved by adding PDT. Palazon and co-workers provided another method to realize this transformation through adding the different amines at room temperature.⁴²² They found the optical properties measured after TMEDA treatment were different from those of the starting solution of CsPbBr_3 NCs. The spectral features (a sharp absorption peak at 317 nm, no absorption in the visible range and no significant green emission) together with XRD patterns indicate the transformation from CsPbBr_3 to Cs_4PbBr_6 NCs (see Figure 37c).

Reversibly, Cs_4PbBr_6 NCs could be transformed back to CsPbBr_3 NCs through an insertion reaction with PbBr_2 .⁴¹¹ As shown in Figure 38, this transformation would lead to the shape change from the hexagonal to cubic structure, as well as the changes of spectral features, including absorption, PL spectra and XRD patterns. The transformation from Cs_4PbBr_6 to CsPbBr_3 enabled the preservation of CsPbBr_3 NCs size and crystallinity. Wu *et al.* reported the water-triggered transformation from Cs_4PbX_6 to CsPbX_3 NCs with tunable optical properties and improved stability in air.⁴¹⁷ Such transformation occurred at the interface of water and a nonpolar solvent, leaving the product of CsPbX_3 NCs in the organic solvent and the byproduct in the water. They highlighted that the high solubility of CsX in water and the interface between nonpolar

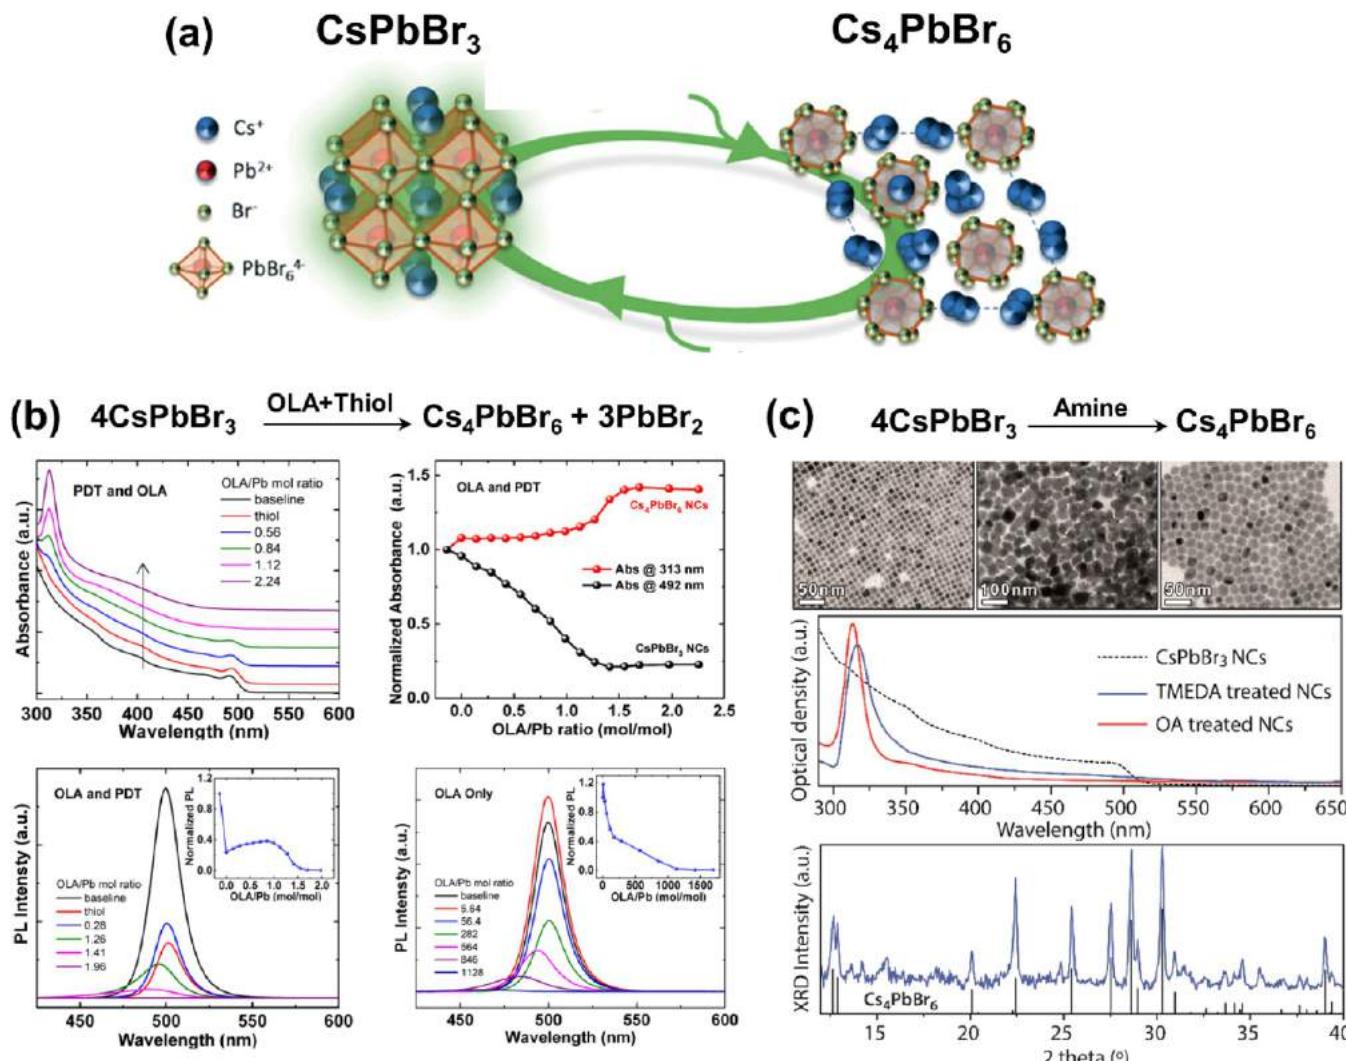


Figure 37. (a) Schematic illustration of the structural transformation between CsPbBr_3 and Cs_4PbBr_6 NCs. Reproduced with permission from ref 420. Copyright 2018 Royal Society of Chemistry. (b) Absorbance spectra, normalized absorbance at two spectral features, and PL spectra of CsPbBr_3 NCs solutions before and after adding different amount of oleylamine with and without PDT. Reproduced from ref 421. Copyright 2017 American Chemical Society. (c) TEM micrographs, absorption spectra, and XRD patterns of CsPbBr_3 NCs before and after the treatment with either tetramethylethylenediamine (TMEDA) or OA. Reproduced from ref 422. Copyright 2017 American Chemical Society.

solvent and water played important roles in the transformation process. In addition, the transformed CsPbBr_3 NCs showed better stability against moisture than those obtained through the hot-injection method. In addition to the phase transformation triggered by PbBr_2 or water, Palazon *et al.* showed that Cs_4PbBr_6 NCs can be transformed into CsPbBr_3 NCs either by thermal annealing or by reaction with Prussian blue.⁴²³ They also proposed that the use of Prussian blue as an additive in 3D CsPbBr_3 films can stabilize the 3D phase by preventing its transformation to other phases. In a recent work, Baranov *et al.* were able to transform Cs_4PbBr_6 NCs to CsPbBr_3 NCs in a controlled way by reaction with poly(maleic anhydride-*alt*-1-octadecene) (PMAO).⁴²⁴ This polymer contains succinic anhydride units that were able to react with the oleylamine ligands bound to the surface of the Cs_4PbBr_6 nanocrystals, forming polysuccinamic acid, which was ultimately responsible for the transformation of Cs_4PbBr_6 to CsPbBr_3 . This reaction scheme is peculiar as the reaction was slow and intermediate Cs_4PbBr_6 – CsPbBr_3 heterostructures

could be isolated. When analyzed under high-resolution transmission electron microscopy (HRTEM), clear epitaxial interfaces were identified between the two domains in individual NCs.

Optical Features of Molecular-like Cs_4PbBr_6 NCs. The peculiar crystal structure of 0D inorganic perovskites with isolated lead-halide octahedra enables the study of the intrinsic properties of an individual octahedron, such as intrinsic Pb^{2+} ion emission,⁴²⁵ large exciton binding energy, and polaron formation energy,^{413,426} as well as the molecular-like blinking behavior.⁴²⁷ From temperature-dependent PL spectra, as given in Figure 39a, non-green-emissive Cs_4PbBr_6 NCs showed spectral splitting feature in the UV range that were originated from Pb^{2+} emissions.⁴²⁵ The high-energy UV emission (around 350 nm) in the non-green-emissive NCs was attributed to the allowed optical transition of Pb^{2+} ions (*i.e.*, $^3\text{P}_1$ to $^1\text{S}_0$), and the low-energy UV emission (around 400 nm) was assigned to the charge-transfer state involved in the host lattice once a Cs^+ ion was replaced by a Pb^{2+} ion (Figure 39b). In addition, the

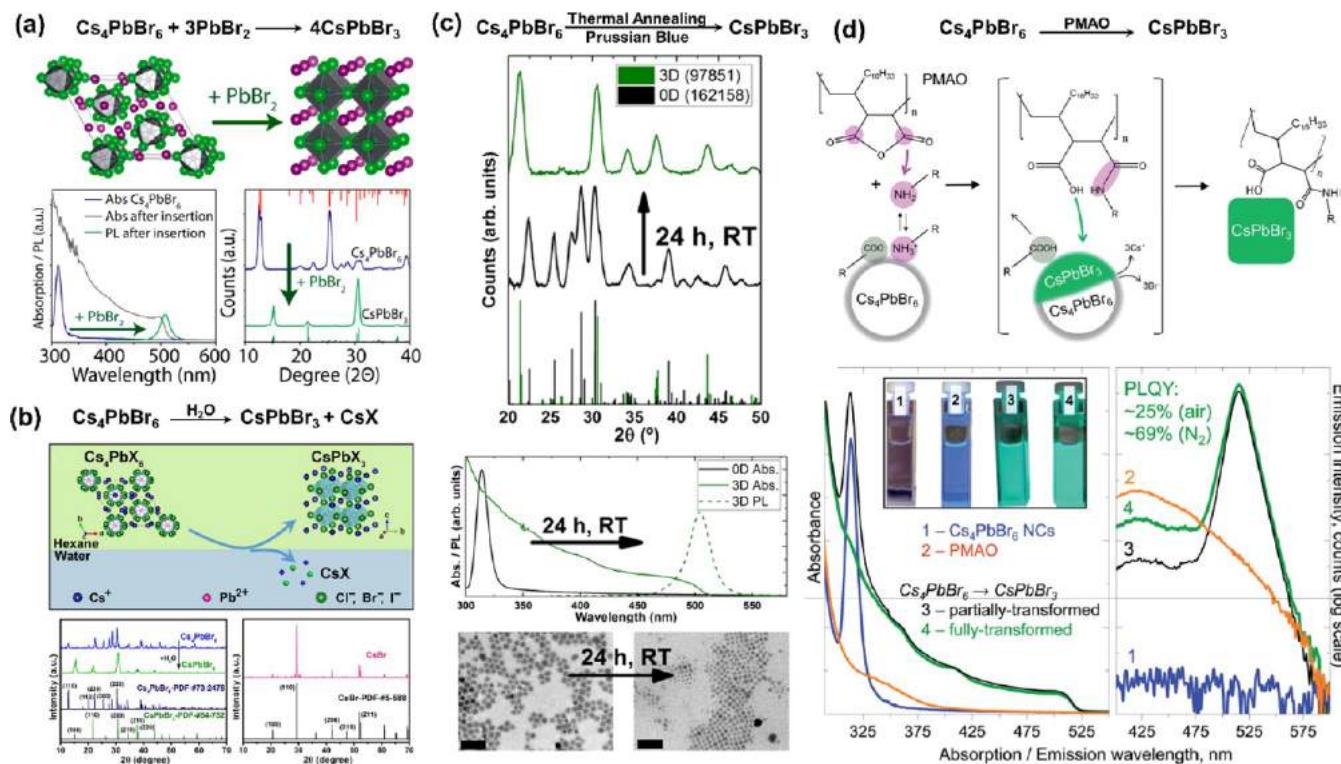


Figure 38. (a) Schematic illustration of phase transformation of the Cs_4PbBr_6 to CsPbBr_3 after insertion of additional PbBr_2 with the optical absorption, PL spectra, and XRD patterns of Cs_4PbBr_6 NCs before and after the insertion reaction. Reproduced from ref 411. Copyright 2017 American Chemical Society. (b) Schematic illustration of crystal structure change and transformation process from Cs_4PbX_6 to CsPbX_3 after water treatment, together with the XRD patterns of Cs_4PbBr_6 NCs before and after adding water. Reproduced from ref 417. Copyright 2017 American Chemical Society. (c) XRD patterns, absorption spectra, and TEM images of Cs_4PbBr_6 NCs transformed to CsPbBr_3 by adding Prussian blue. Reproduced from ref 423. Copyright 2017 American Chemical Society. (d) Schematic illustration of the transformation of Cs_4PbBr_6 into CsPbBr_3 NCs induced by PMAO, together with optical absorption and emission spectra of initial Cs_4PbBr_6 NCs, PMAO, and partially and fully transformed NCs in toluene solutions. Reproduced with permission under Creative Common CC-BY 3.0 license from ref 424. Copyright 2020 Royal Society of Chemistry.

energy transfer from Pb^{2+} ions to green luminescent centers occurred in the emissive Cs_4PbBr_6 NCs, in addition to the broad-band UV emission.

Meanwhile Yin and co-workers underlined that Cs_4PbBr_6 behaves like a molecule by demonstrating its low electrical conductivity and mobility, as well as large polaron binding energy.⁴²⁶ As shown in Figure 39c, they observed an additional positive broad-band signal above 530 nm (*i.e.*, polaron absorption) in the transient absorption spectra of the Cs_4PbBr_6 thin film and the corresponding kinetics probed at 600 nm showed a lifetime of ~ 2 ps. This confirmed the generation of small polarons with large binding energies and tight localization at individual $[\text{PbBr}_6]^{4-}$ octahedra. The short lifetime of the polaron state can be understood by *ab initio* molecular dynamics calculations, showing the central octahedron recovered to the neutral state after 1.2 ps starting from the initial polaronic state (Figure 39d). Thus, after photo-excitation, the structure deformation of single octahedra leads to the formation of localized polarons with short lifetime and limited transport in the Cs_4PbBr_6 .

The molecular behavior of Cs_4PbBr_6 was further proved by the photon emission from individual NCs.⁴²⁷ Cs_4PbBr_6 NCs showed a burst-like emission behavior with a uniform distribution of PL lifetimes induced by increasing the excitation, and meanwhile exhibited a photobrightening effect because of several emissive centers within the same NC (Figure 39e). Actually, at lower excitation levels, both 3D and

0D perovskite NCs exhibited similar single-photon emission behavior, independent of their structural dimensionalities and NC size. Therefore, the emission statistics of Cs_4PbBr_6 and CsPbBr_3 NCs were similar to those of individual molecular fluorophores, which are different from the traditional semiconductor quantum dots.

The intrinsic Pb^{2+} ion emissions of molecular-like 0D perovskites motivated several studies of tuning the optical emissions of Cs_4PbBr_6 NCs. Arunkumar and co-workers studied the optical behavior of Cs_4PbX_6 NCs through manganese (Mn^{2+}) doping at Pb sites.⁴²⁸ They demonstrated that the incorporation of Mn^{2+} dopants can stabilize the Cs_4PbX_6 structure and suppress the formation of CsPbX_3 impurities by the enhanced octahedral distortion. They also confirmed the incorporation of Mn^{2+} in the 0D Cs_4PbX_6 lattice by the structural characterizations, PL spectra, and PL lifetime (Figure 40a). Moreover, they achieved a high PLQY of Mn^{2+} emission in both colloidal (29%) and solid (21%, powder) forms and attributed the enhanced PLQY to the synergistic effect of structure-induced spatial confinement of Cs_4PbX_6 and electronically decoupled PbX_6 octahedra. Zou *et al.* proposed another method to tailor the band gap of Cs_4PbBr_6 NCs to the blue spectral region by changing the local coordination environment of isolated $[\text{PbBr}_6]^{4-}$ octahedra in the Cs_4PbBr_6 through Sn^{2+} doping.⁴²⁹ Due to the distinctive Pb^{2+} -poor and Br^- -rich reaction environment, the Sn^{2+} ions can be successfully incorporated into the Cs_4PbBr_6 NCs, giving rise

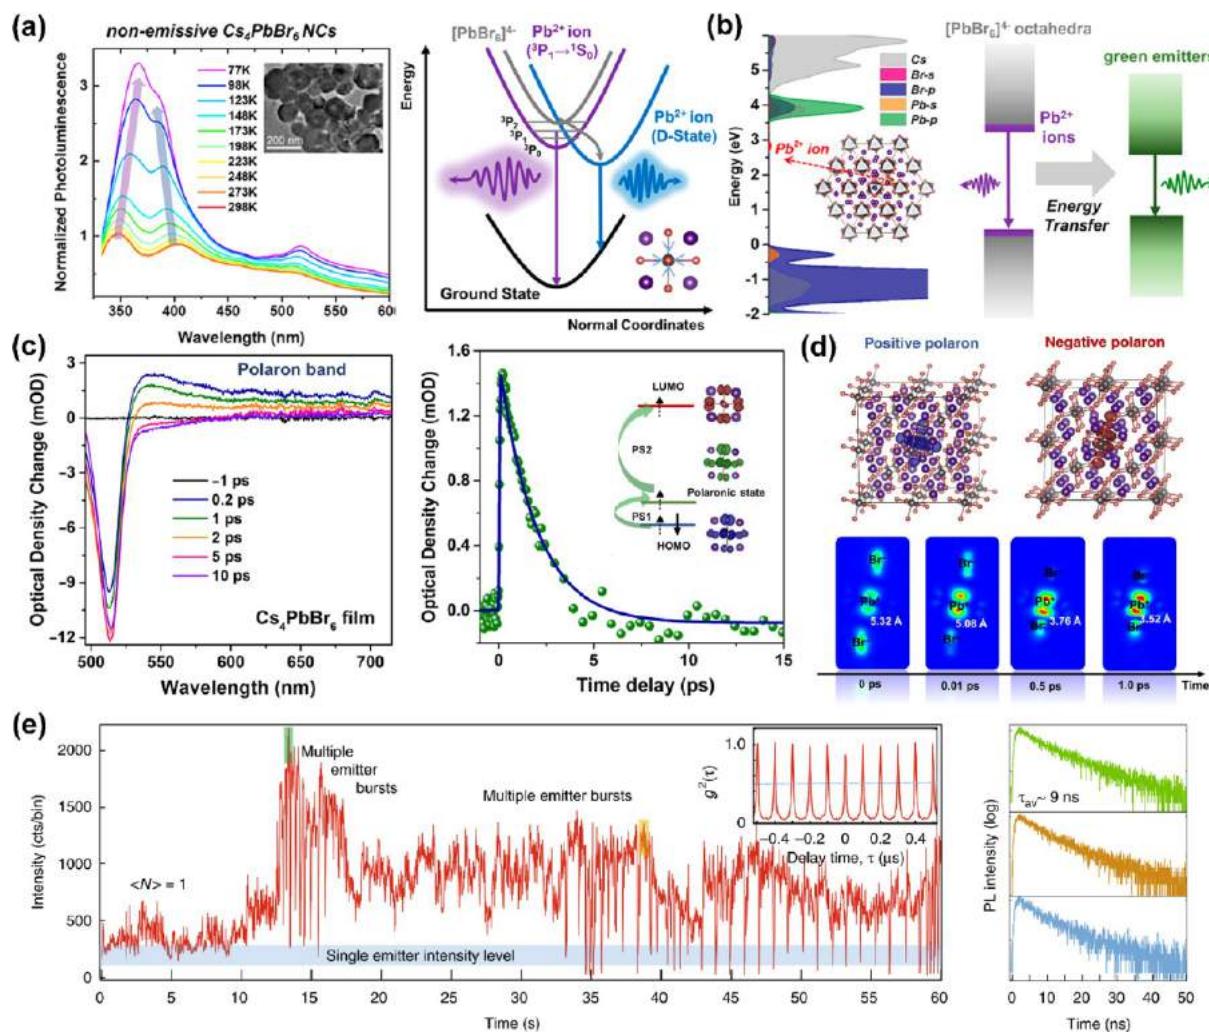


Figure 39. (a) Temperature-dependent PL spectra of non-emissive (non-green-emissive) Cs_4PbBr_6 NCs and diagram of $^3\text{P}_1$ to $^1\text{S}_0$ and D-state emissions from Pb^{2+} ions. Reproduced from ref 425. Copyright 2017 American Chemical Society. (b) Projected density of states of Cs_4PbBr_6 supercell after the replacement of a Cs^+ with a Pb^{2+} ion and diagram of UV and visible emissions of Cs_4PbBr_6 NCs. Reproduced from ref 425. Copyright 2017 American Chemical Society. (c) Transient absorption spectra and photoexcitation kinetics probed at 600 nm of Cs_4PbBr_6 thin films. Reproduced with permission under Creative Common CC BY-NC 4.0 license from ref 426. Copyright 2017 American Association for the Advancement of Science. (d) Charge density distributions for the Cs_4PbBr_6 supercell with a positive/negative polaron located in the central octahedron and charge density mapping of conduction band maximum for the central octahedron at selected times. Reproduced with permission under Creative Common CC BY-NC 4.0 license from ref 426. Copyright 2017 American Association for the Advancement of Science. (e) Blinking in individual Cs_4PbBr_6 NCs with the emergence of multiple emitters. Reproduced with permission under Creative Common CC BY from ref 427. Copyright 2019 The Authors.

to the coexisting point defects of substitutional (Sn_{Pb}) and interstitial (Br_i) for an ultranarrow blue emission at ~ 437 nm (Figure 40b). They proposed an unusual electronic dual-band-gap structure, composed of the additional band gap (2.87 eV) and original 0D band gap (3.96 eV), to be at the origin of the ultranarrow blue emission.

Origin of Green Emission in Cs_4PbBr_6 NCs. Although the molecular-like quantum optoelectronic behavior of Cs_4PbBr_6 NCs is well-studied, the origin of their green emission is still not clear. Several emission mechanisms have been proposed in the literature, including the embedded 3D CsPbBr_3 impurities, intrinsic point defects, and 2D Cs_2PbBr_4 inclusion. For instance, Quan *et al.* confirmed the efficient green-emitting CsPbBr_3 NCs were embedded in air-stable Cs_4PbBr_6 microcrystals, *i.e.*, the coexistence of NCs and the matrix, by powder XRD, high-resolution transmission electron microscopy (HRTEM) and scanning electron microscope

(SEM) imaging (Figure 41a).⁴³⁰ They suggested the lattice matching between the CsPbBr_3 NCs and the Cs_4PbBr_6 matrix contributed to improved passivation and such spatial confinement can enhance the radiative rate of the NCs. Recently, Qin *et al.* also suggested the presence of CsPbBr_3 impurities in Cs_4PbBr_6 by identifying the Raman difference between emissive and non-emissive Cs_4PbBr_6 . They found that the Raman spectrum of emissive Cs_4PbBr_6 was identical to that of the non-emissive case, but it contains an additional Raman band at ~ 29 cm^{-1} that replicated the doublet at 28-30 cm^{-1} of CsPbBr_3 (Figure 41b).⁴³¹ The concentration of CsPbBr_3 was estimated to 0.2% in volume and this was below the typical XRD sensitivity. They observed a fast red-shifting, diminishing, and eventual disappearance feature of green emission by employing a diamond anvil cell to probe the response of luminescence centers to hydrostatic pressure (Figure 41c). This can help exclude the Br vacancies as the luminescent

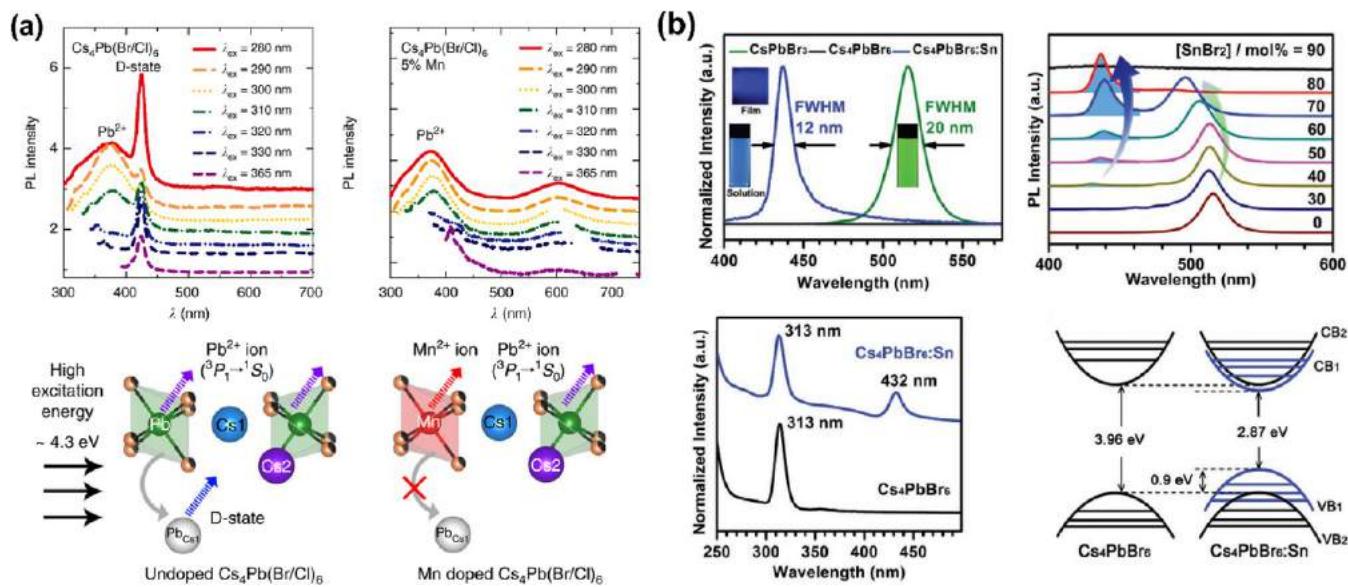


Figure 40. (a) PL spectra of undoped $\text{Cs}_4\text{Pb}(\text{Br}/\text{Cl})_6$ and Mn^{2+} -doped $\text{Cs}_4\text{Pb}(\text{Br}/\text{Cl})_6$ measured at different excitation wavelengths and origin of Pb^{2+} emissions and D-state in $\text{Cs}_4\text{Pb}(\text{Br}/\text{Cl})_6$ without and with Mn^{2+} doping. Reproduced with permission under a Creative Commons CC BY 4.0 license from ref 428. Copyright 2018 The Authors. (b) PL spectra of CsPbBr_3 NCs, Sn-doped Cs_4PbBr_6 NCs, and CsPbBr_3 NCs, and UV-vis absorption spectra of pure and Sn-doped Cs_4PbBr_6 perovskite NCs, together with the schematic illustration of the possible electronic dual-band-gap structure for the Cs_4PbBr_6 NCs before and after Sn^{2+} doping. Reproduced with permission from ref 429. Copyright 2019 John Wiley & Sons, Inc.

centers. Riesen *et al.* concluded that the green emission from Cs_4PbBr_6 is due to nanocrystalline CsPbBr_3 impurities using cathodoluminescence imaging and energy-dispersive X-ray (EDX) measurements.⁴³² The CL imaging and spectroscopy showed the presence of small crystals embedded in between larger crystallites of Cs_4PbBr_6 which emitted around 520 nm (Figure 41d). EDX showed that the smaller crystal inclusions have a Pb/Br ratio that was approximately two times higher, confirming the CsPbBr_3 phase (Figure 41e).

Many other groups have argued that the green emission of Cs_4PbBr_6 is not from CsPbBr_3 impurities but an intrinsic property of Cs_4PbBr_6 because of (*i*) the absence of diffraction peak and pattern of CsPbBr_3 , (*ii*) the failure of halogen exchange, and (*iii*) no match of the emission peak for the small-size CsPbBr_3 NCs. Yin *et al.* have demonstrated that the bromide vacancy (V_{Br}) of Cs_4PbBr_6 has a low formation energy and is a relevant defect level that contributes to the green emission.⁴³³ As shown in Figure 42a, in the Pb-rich/Br-poor condition, V_{Br} was the dominant defect and had a transition level energy of ~ 2.3 eV located above the valence band maximum (VBM); Pb- and Cs-related vacancies showed a deep transition level (-0.5 eV below the VBM), and the other antisites all had deep transition levels within the band gap. To confirm the green emission from V_{Br} point defects, they synthesized Cs_4PbBr_6 NCs under different conditions by controlling the HBr amount, and found the PL intensity increased when increasing the concentration of Br defects and the highest PLQY was achieved in Br-deficient Cs_4PbBr_6 NCs (Figure 42b). Moreover, their state-of-the-art characterizations including HRTEM further confirmed the purity of the 0D phase of Br-deficient green-emissive Cs_4PbBr_6 NCs and also excluded the presence of CsPbBr_3 NCs impurities. The theory concerning the inclusion of Br defects was recently supported by Cha and co-workers based on the characteristic magnetic behavior of non-emissive and green-emissive Cs_4PbBr_6 perovskite crystals.⁴³⁴ They demonstrated the presence of defects in

green-emissive Cs_4PbBr_6 and the extremely low concentration of a CsPbBr_3 phase in both non-emissive and green-emissive crystals based on the analysis of ^{133}Cs magic-angle-spinning (MAS) NMR spectra (Figure 42c).

Jung and co-workers have a different theoretical view about defect properties of Cs_4PbBr_6 .⁴³⁵ They showed that the Br_{Cs} defects led to the formation of molecular Br_3 -type species that exhibited a range of optical transitions in the visible range, and the green luminescence can be from the emission of optically excited Br_3 to its ground state. Based on the analysis of the lowest-lying electronic excitation energy as a function of the Br–Br distance (Figure 42d), they found Br_3^- and Br_3^{2-} provide $\text{S}_1 - \text{S}_0$ energy differences in the range of green emission (~ 2.3 eV). They suggested the presence of a radiative mechanism with visible-light emission in Br_3^- molecular species that could contribute to the green emission in Cs_4PbBr_6 upon tribromide defect formation.

Ray and co-workers proposed that a 2D Cs_2PbBr_4 inclusion may be responsible for the green emission of Cs_4PbBr_6 NCs although they found no conclusive experimental evidence supporting this claim.⁴³⁶ They found the solvodynamic size of the lead bromide species played a critical role in determining the Cs–Pb–Br composition of the precipitated powders, *i.e.*, the smaller species favored the precipitation of Cs_4PbBr_6 and larger species favored the formation of CsPbBr_3 under the same experimental conditions (Figure 42e). Therefore, Cs_4PbBr_6 has a higher tendency to be precipitated out from solutions with stronger coordinating solvents to Pb^{2+} , lower absolute concentration of the precursors, and higher $\text{CsBr}/\text{PbBr}_2$ ratios, as compared to 3D CsPbBr_3 counterpart. They concluded that 3D impurities might not be the only source of the emission and high PLQY and proposed an impurity of 2D Cs_2PbBr_4 may also contribute to the green emission.

Optoelectronic Applications of Cs_4PbBr_6 Microcrystals and Nanocrystals. Despite the unclear origin of green emission in Cs_4PbBr_6 NCs, the high PL intensity and PLQY of

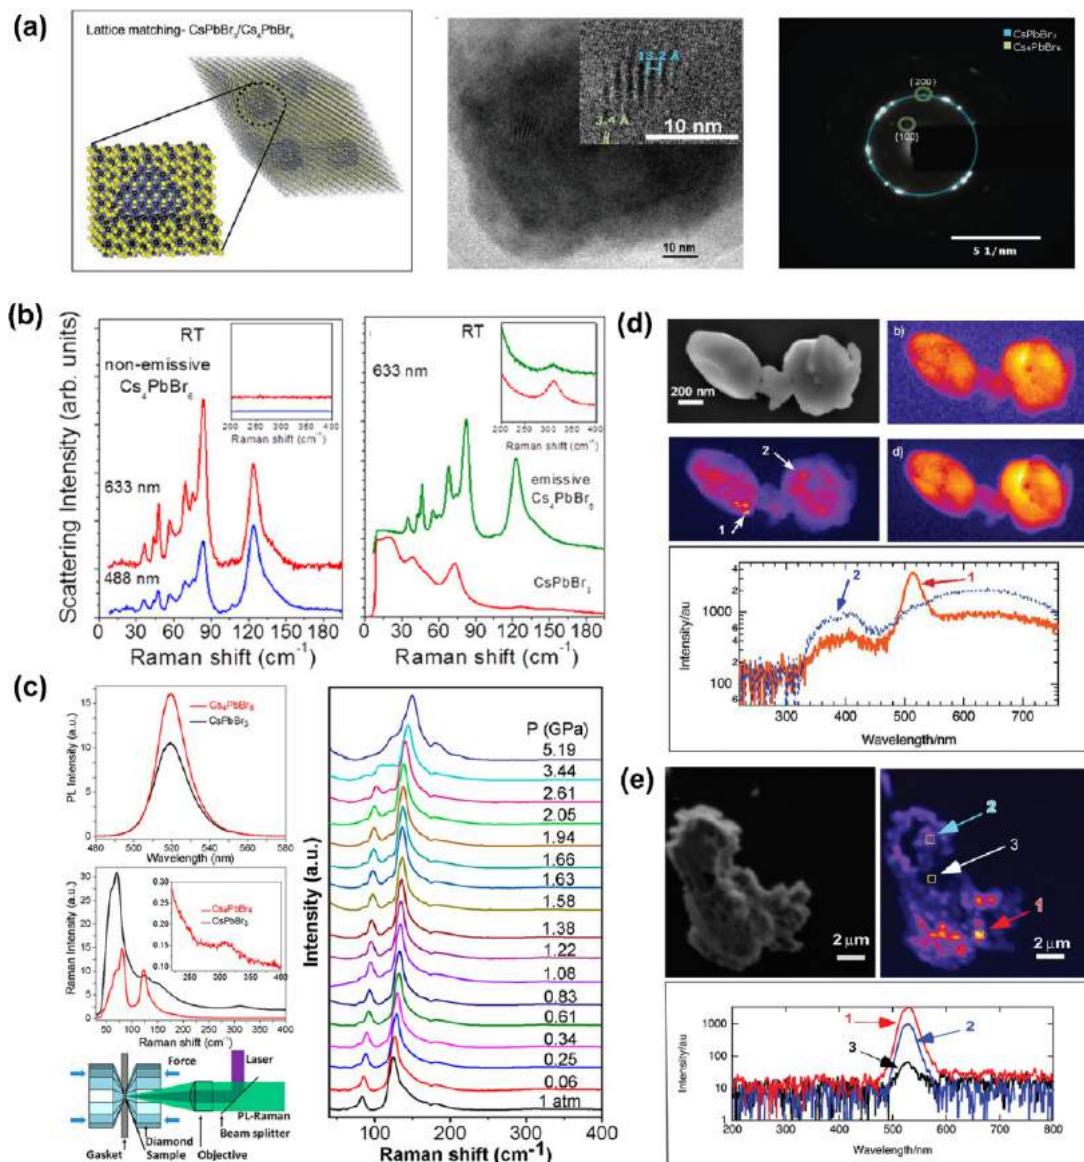


Figure 41. (a) Theoretical model of cubic CsPbBr₃ perovskite NCs embedded in a matrix made of Cs₄PbBr₆ together with a HRTEM image of a CsPbBr₃-in-Cs₄PbBr₆ crystal. Reproduced with permission from ref 430. Copyright 2017 John Wiley & Sons, Inc. (b) Raman spectra of CsPbBr₃ microcrystals, non-emissive and emissive Cs₄PbBr₆ at room temperature. Reproduced from ref 431. Copyright 2019 American Chemical Society. (c) PL spectra, Raman spectra, and diamond anvil cell for confocal pressure Raman-PL and pressure evolution of Raman of emissive Cs₄PbBr₆. Reproduced from ref 431. Copyright 2019 American Chemical Society. (d) SEM micrograph of a particle aggregate of Cs₄PbBr₆ with CL band-pass images. Reproduced with permission from ref 432. Copyright 2018 Royal Society of Chemistry. (e) SEM micrograph of Cs₄PbBr₆ aggregate with CL image and CL spectra for three regions. Reproduced with permission from ref 432. Copyright 2018 Royal Society of Chemistry.

Cs₄PbBr₆ NCs make them interesting for the applications in the optoelectronic devices.⁴⁴⁰ Bao *et al.* reported a synthesis method to obtain highly stable Cs₄PbBr₆ microcrystals (MCs) using a microfluidic system.⁴³⁷ They incorporated Cs₄PbBr₆ MCs with K₂SiF₆:Mn⁴⁺ phosphor onto InGaN blue chips to fabricate the white light-emitting diodes (Figure 43a). The white LED device exhibited a wide color gamut of 119% of National Television Standards Committee (NTSC) standard and a luminous efficiency of 13.91 lm/W. Sun *et al.* developed an antisolvent approach to obtain the phase-pure Cs₄PbBr₆ MCs exhibiting intense PL centered at 518 nm with a PLQY of ~30% and a large binding energy of 267 meV.⁴³⁸ They revealed the agreement between the PL excitation spectrum and localized optical absorption of Pb²⁺ in isolated [PbBr₆]⁴⁻

octahedra and confirmed that the green emission was an intrinsic feature of Cs₄PbBr₆. Moreover, they demonstrated the single- and multimode lasing resonances in individual Cs₄PbBr₆ MCs by optical pumping, showing a high photo-stability even upon rather intense optical pumping (Figure 43b). Cs₄PbBr₆ NCs can be used in luminescent solar concentrators (LSCs) (Figure 43c) absorber as they meet the requirements of small absorption/emission spectral overlap, high PLQY, robust stability and ease of synthesis. Zhao and co-workers fabricated semitransparent large-area LSCs using Cs₄PbBr₆ NCs and the optimized LSCs exhibited an external optical efficiency of 2.4% and a power conversion efficiency of 1.8% (100 cm²).⁴³⁹ These results suggest that 0D perovskite MCs and NCs are promising candidates for high-

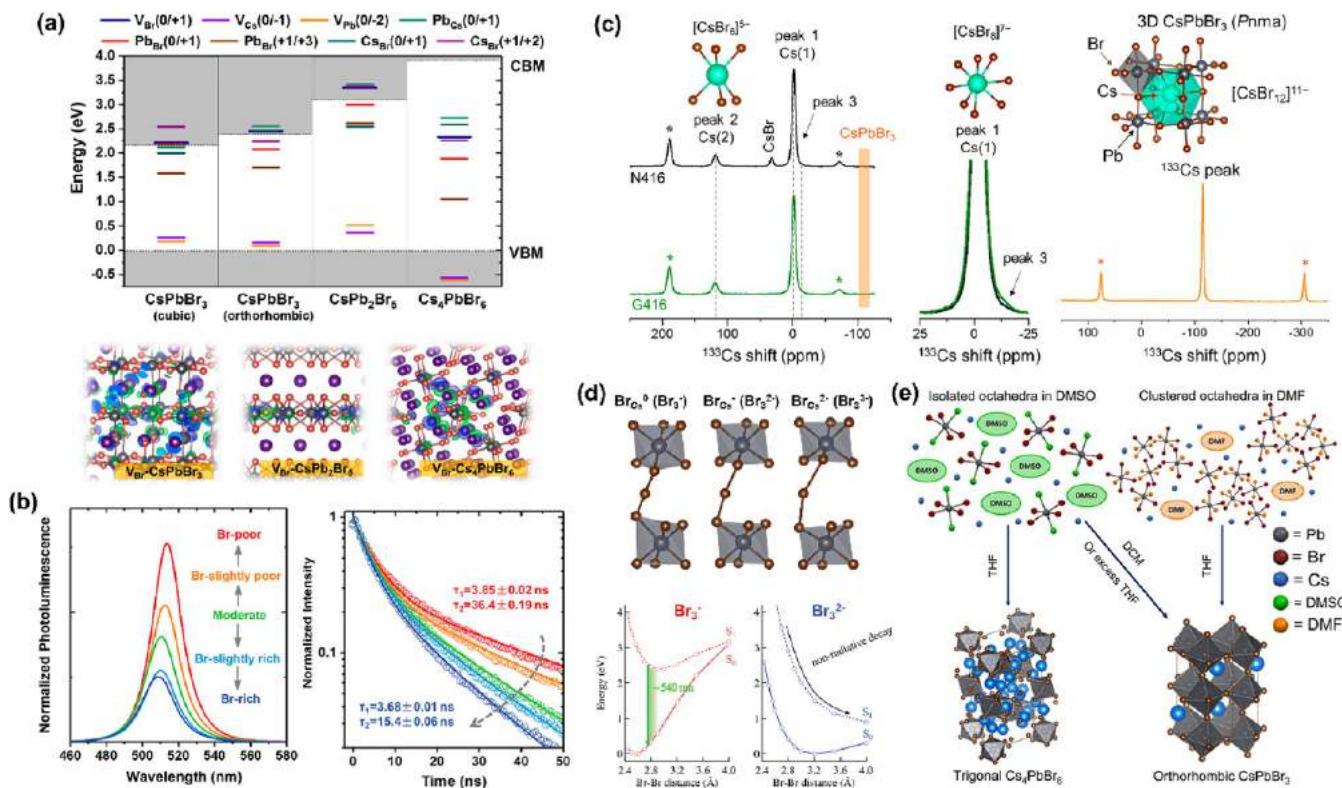


Figure 42. (a) Calculated defect charge transition levels and charge density distributions of V_{Br} defect states for $CsPbBr_3$, $CsPb_2Br_5$, and Cs_4PbBr_6 . (b) Normalized PL spectra and time-resolved PL spectra of Cs_4PbBr_6 NCs under different growth conditions. Reproduced from ref 433. Copyright 2018 American Chemical Society. (c) ^{133}Cs MAS NMR spectra and corresponding magnified spectra (25 to -25 ppm) of non-emissive and green-emissive Cs_4PbBr_6 obtained at 9.4 T and a spinning rate of 10 kHz at 300 K, together with ^{133}Cs MAS NMR spectra of $CsPbBr_3$ perovskite crystal. Reproduced from ref 434. Copyright 2020 American Chemical Society. (d) Local structure associated with point defect species in Cs_4PbBr_6 and relative potential energy surfaces of ground state S_0 and first excited state S_1 as a function of the Br-Br distance for Br_3^- and Br_3^{2-} . Reproduced with permission from ref 435. Copyright 2019 Royal Society of Chemistry. (e) Schematic diagram of the effect of the solvodynamic size and solvent-antisolvent pair on the formed $CsPbBr_3$ and Cs_4PbBr_6 phases. Reproduced under a Creative Commons CC-BY-NC-ND license from ref 436. Copyright 2019 American Chemical Society.

efficiency optoelectronic devices covering a similar application sphere as 3D perovskite NCs.

SURFACE COATING STRATEGIES FOR STABILITY IMPROVEMENT

Considering the intrinsic ionic nature,^{14,417,441} the durability of MHP NCs against moisture, oxygen, light and high temperatures is still a significant challenge that has limited their further development and practical applications. Over the years, significant studies have been devoted to the encapsulation of perovskite NCs in various materials either in the form of core-shell NCs or NCs in a matrix as illustrated in Figure 44. The encapsulation process can be carried out by either *in situ* synthesis or post-synthesis surface coating. Encapsulation by inert materials has proven to be a feasible and effective approach to prevent the decomposition and enhance stability, enabling them to survive under water/photo/thermal treatment.^{278,329,442–446} It has been reported that $CsPbX_3$ NCs have a high defect-tolerance,²³ however, the surface traps that probably assist the nonradiative process are still non-negligible.⁸⁸ In addition to surface passivation with molecular ligands, a suitable encapsulation strategy (Figure 44) can also efficiently remove or fix the quenching sites located on the surface, and thus suppress the nonradiative recombination.³⁰¹ Hence, the encapsulation always improves the photophysical properties of MHP NCs owing to the significant passivation

effect.^{447,448} In addition, encapsulation also protects against reactive oxygen species.⁴⁴⁹ Furthermore, the energy- and charge-transfer process within MHP NCs can also be tuned with semiconductor shells on their surface. In some cases, brighter PL emission can be achieved by the introduction of wider-gap semiconductors to fabricate type-I composite. In this type, the foreign semiconductor shell has a higher conduction band and a lower valence band compared to $CsPbX_3$, leading to confinement of photogenerated carriers.^{364,427,430,450–452} On the contrary, PL quenching occurs in type-II heterostructure when the band gap of $CsPbX_3$ NCs overlaps with another semiconductor, favoring the charge diffusion, transfer, and finally separation.^{365,427} Due to the distinctly different carrier performance, these heterostructures with type-I and type-II can be applied in LEDs and photocatalysis, respectively. Despite recent progress in the synthesis of perovskite NCs, further advances in stability enhancement, surface passivation, and charge confinement/separation endowed by encapsulation are still necessary to advance the field of perovskite NCs toward commercial optoelectronic applications. Different strategies for encapsulating perovskite NCs to enhance their stability are discussed below. It should be noted that the conditions (e.g., concentration, whether the NCs are in colloidal solution or in powder form, temperature, solvent, time, ligand density, shell thickness in the case of core-shell NCs) used for the comparison of the stability of perovskite NCs is different in

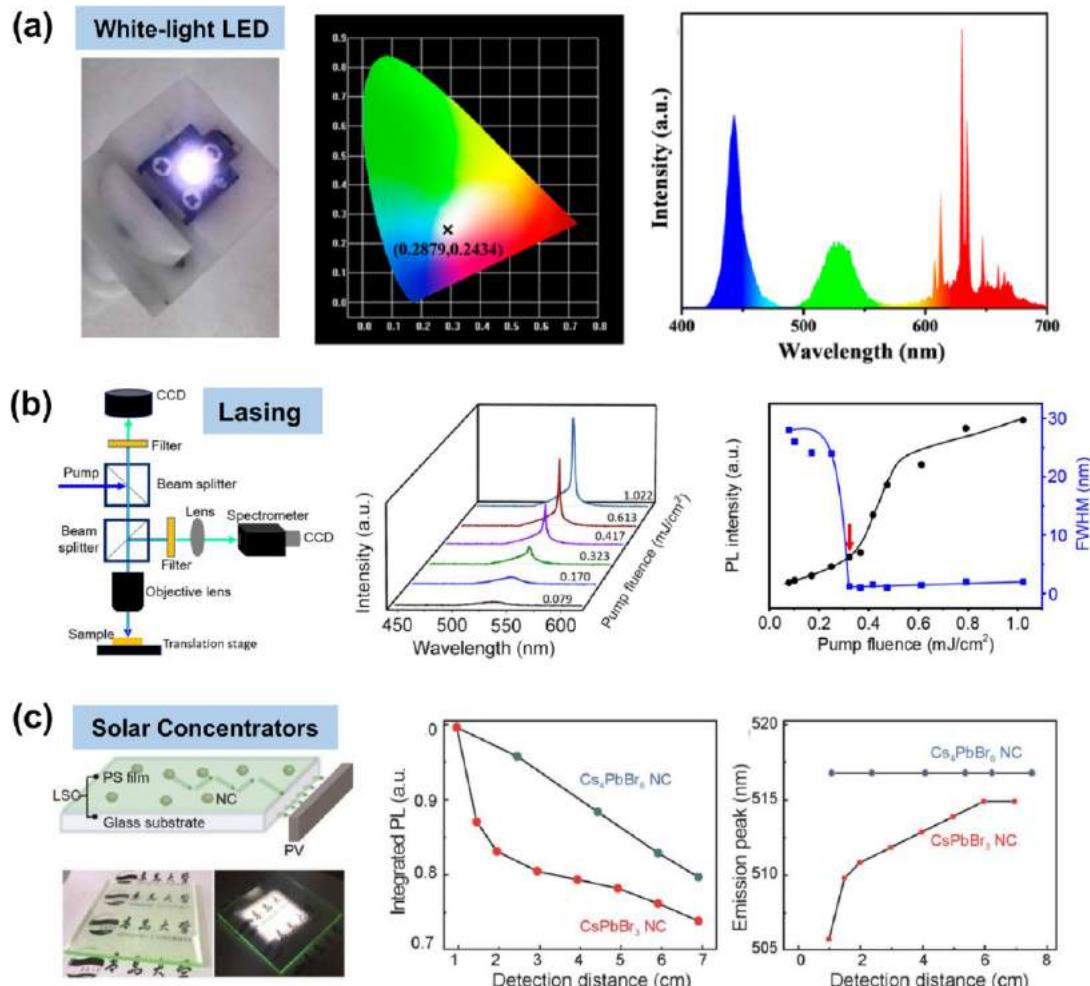


Figure 43. (a) Photographs of LED devices fabricated with Cs_4PbBr_6 MCs and $\text{K}_2\text{SiF}_6:\text{Mn}^{4+}$ phosphor, color coordinates of the white LEDs, and electroluminescent spectra of the white LED. Reproduced from ref 437. Copyright 2018 American Chemical Society. (b) Schematic of the micro-PL setup for imaging and detection of the PL signal of an individual Cs_4PbBr_6 microcrystal and evolution of the PL spectra with the pump fluence and dependence of the PL intensity and fwhm on the pump fluence. Reproduced from ref 438. Copyright 2018 American Chemical Society. (c) Scheme of an LSC and photographs of the LSC comprising perovskite NCs under ambient and one sun illumination and integrated PL intensity and emission peak positions as a function of detection distance. Reproduced with permission from ref 439. Copyright 2019 John Wiley & Sons, Inc.

different studies. Therefore, the discussion is mainly limited to a specific example in each case.

Encapsulation at Multiple-Particle Level. Despite the on-going intensive efforts and a plethora of conducted studies, metal-halide perovskite NCs are still suffering from rather poor stability against many common factors such as oxygen, humidity, light illumination, and heat. The identification of suitable encapsulation of perovskite NCs is thus an ongoing task, and several types of protective materials have been suggested, such as silica, organic polymers, metal oxides, metal salts, etc.

Silica coating of conventional semiconductor quantum dots (*i.e.*, CdSe QDs) has become well-established and often used for MHP NCs as well, due to the nontoxic nature, mechanical robustness, high thermal stability, and good optical transmission of this material.^{453,454} However, as the conventional hydrolysis process to form SiO_2 shell needs some amount of water, this may appear detrimental for the stability and optical properties of perovskites. Overall, the use of silica encapsulation strategy for MHP NCs requires the right balance between the hydrolysis rate and the ability to form compact and dense

SiO_2 protective shells. There have been few attempts to encapsulate MHP NCs in silica matrix using traditional precursors tetraethyl orthosilicate (TEOS)^{455,456} and octadecyltrimethoxysilane,⁴⁵⁷ while other precursors such as tetramethyl orthosilicate⁴⁵⁸ and APTES⁴⁴⁵ with higher hydrolysis rate were employed to enable the faster formation of a SiO_2 protective layer under the assistance of a trace amount of water, in which perovskite NCs are able to withstand.⁴⁵⁹ The latter silicate precursors enable to maintain the original high PLQY and narrow PL emission of both organic-inorganic (methylammonium-based) and all-inorganic (cesium-based) lead-halide perovskite NCs for a longer time: for example, the APTES shelled $\text{CsPb}(\text{Br/I})_3$ NCs maintained 95% PLQY after 3 months of storage.

The incorporation of multiple perovskite NCs inside mesoporous silica spheres has been demonstrated to be a good option to improve their thermal stability and photo-stability, with a final aim to enhance the device performance.^{444,460} High-angle annular dark-field scanning transmission electron microscopy (HAADF-STEM) was used to confirm the presence of several CsPb_2Br_5 NCs in an individual

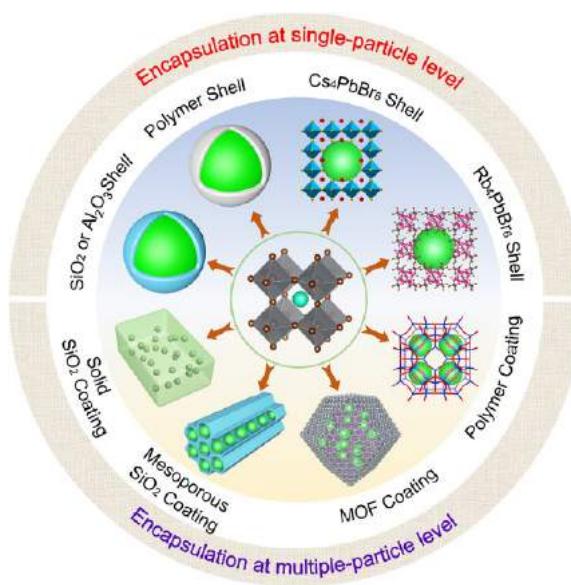


Figure 44. Schematic overview of different types of shell materials employed for coating on perovskite NCs to improve their stability toward heat, moisture, water, and other environmental stresses.

mesoporous silica particle, as shown in Figure 45a. These samples were used to fabricate white light-emitting devices (WLED).⁴⁶⁰ Superhydrophobic sponge-like silica aerogels acted as a scaffold to accommodate $\text{CH}_3\text{NH}_3\text{PbBr}_3$ NCs and could well-preserve both the structure and optical properties of these perovskites due to their amorphous phase and high optical transparency.⁴⁶¹ This system was then demonstrated to serve as a sensitive fluorescence SO_2 gas sensor with a reversible quench-and-recovery in the emission response.⁴⁶¹

Some other silica-related compounds have been explored as well to protect lead-halide perovskite NCs from water and humid environment. Polyhedral oligomeric silsesquioxane with a cage-like structure and functional thiol group able to coordinate with the surface of CsPbBr_3 NCs (Figure 45b) was used as efficient encapsulating material able to protect these perovskites from water.⁴⁶² The encapsulated powdered samples kept their emission as a dispersion in water for more than 10 weeks, as shown in Figure 45c, and also prevented mixed-anion (Br/I) perovskite powders from ion exchange, thus enabling their use as light-emitting layers in down-conversion WLEDs.⁴⁶²

For the conventional hydrolysis process to form a SiO_2 shell, the involved water can cause irreversible damage to the CsPbX_3 NCs. On the other hand, the densification extent of SiO_2 produced by the hydrolysis process is not enough to prevent the penetration of water to the inner CsPbX_3 NCs. To increase the densification extent of SiO_2 and improve the stability of CsPbX_3 NCs, a high-temperature annealing process can promote more densely cross-linked structure of SiO_2 , but the annealing temperature could not exceed 100 °C due to the severe surface oxidation or fusing of CsPbX_3 NCs. In view of this, Zhang *et al.*²⁸³ proposed a facile strategy to synthesize ceramic-like stable and highly luminous CsPbBr_3 NC through template-confined solid-state synthesis and *in situ* encapsulation based on the strategic disintegration of silicon molecular sieve (MS) templates at high temperatures (Figure 45d). The synthesis process is a solid-state reaction at high temperature without organic solvents and organic ligands. Due to the encapsulation of dense SiO_2 at high temperature (500–800

°C), the as-prepared $\text{CsPbBr}_3\text{--SiO}_2$ powders exhibited comparable operation stability as the commercial ceramic phosphors (Figure 45e,f).²⁸³ In addition, a high-temperature solid-state reaction has been used to crystallize CsPbX_3 NCs in glasses, and the obtained CsPbX_3 NCs encapsulated with glasses present high PLQY and robust stabilities to moisture, temperature, and UV light irradiation.^{463–465} In a recent work, An *et al.*⁴⁶⁶ have been able to grow CsPbBr_3 NCs inside the pores of mesoporous silica using a molten salt approach at temperatures as low as 350 °C. The specific combination of salts enabled at the same time a high PLQY and a sealing of the pores, such that the NCs were effectively isolated from the external environment. A clear proof of the stability of these composites was given by the preservation of their emission properties even if they were immersed in aqua regia for several weeks.

The encapsulation within an organic (especially, hydrophobic) polymer hosts is yet another popular choice to improve the resistance of perovskite NCs toward harmful environments such as moisture and oxygen. Zhang *et al.* demonstrated successful encapsulation of CsPbBr_3 NCs using polyvinylpyrrolidone (PVP) and used them as luminescent probes for intracellular imaging in an aqueous environment, as illustrated in Figure 45g.⁴⁴² In addition to PVP, a number of other polymer matrices, including polystyrene (PS),⁴⁶⁷ polycarbonate (PC),³⁸⁶ polyurethane,⁴⁶⁸ PMMA,⁷³ poly(lauryl methacrylate),⁴⁶⁹ and ethylene vinyl acetate⁴⁷⁰ were employed as protective coatings for perovskite NCs. The protection strategies for perovskite NCs employing those different polymers can be classified into two major categories: *in situ* fabrication from suitable precursors, and post-preparative encapsulation of presynthesized perovskite nanoparticles (the previously mentioned POSS encapsulation technology⁴⁶² belongs to the latter one, as shown in Figure 45b). Within the former strategy, Hintermayr *et al.* used nanocavities formed by amphiphilic block copolymer PS-*b*-P2VP (a combination of hydrophilic P2VP part and hydrophobic PS) which provided a suitable space for the spontaneous nucleation of perovskite precursors.⁴⁷¹ Core/shell micelles serving as nanoreactors for the *in situ* formation of perovskite NCs were obtained upon the introduction of antisolvents such as toluene and were composed from the P2VP part as a core and the PS as an outer shell. However, the use of the polymer-coated perovskite composites in LEDs may be problematic, as large applied voltages and unavoidable heat generation during the device operation may induce polymer degradation and thus the emission quenching or undesirable shifts.

Capitalizing upon the previous experience with conventional semiconductor QDs,^{472–474} metal oxides such as alumina (Al_2O_3), TiO_2 , and ZnO have been recently applied to shelter perovskite NCs. Atomic layer deposition and wet-chemical template method are two major fabrication routes for metal oxide deposition,^{475–477} while the high temperature used in the annealing process may be an issue resulting in undesirable decomposition of perovskite NCs. It has been reported that the decomposition of CsPbBr_3 NCs could happen when porous TiO_2 matrix was annealed at just 85 °C.^{365,478} However, CsPbX_3 NCs synthesized by the template confined solid synthesis in mesoporous Al_2O_3 at 800 °C showed high PLQY and outstanding thermal stability beyond to 300 °C.⁴⁷⁹ Metal-organic frameworks (MOFs) composed of metal ions and bridging organic ligands were also considered as a matrix able to protect and preserve the emission of perovskite NCs in

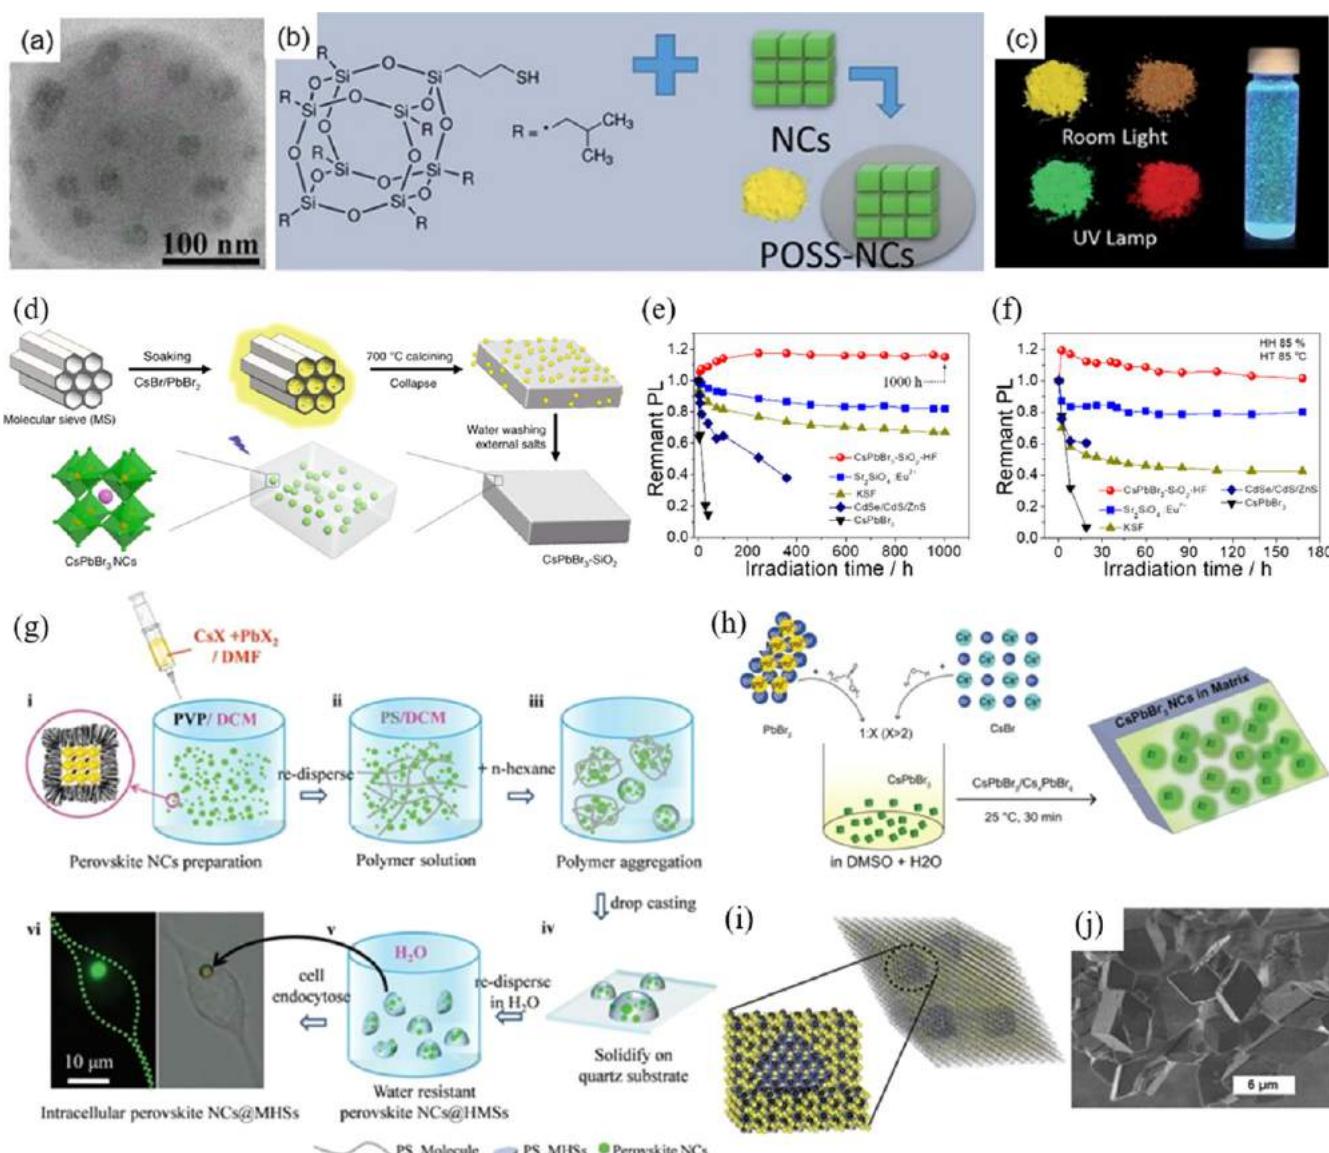


Figure 45. (a) HAADF-STEM image of several CsPbBr₃ NCs embedded within a mesoporous silica sphere. Reproduced with permission from ref 460. Copyright 2017 Royal Chemical Society. (b) Structure of thiolated polyhedral oligomeric silsesquioxane (POSS) and illustration of the coating process of POSS on presynthesized perovskite NCs. (c) Photographs of POSS-coated green-emitting CsPbBr₃ and red-emitting CsPb(Br/I)₃ powders under room light and UV light and a dispersion of green-emitting POSS-CsPbBr₃ NCs in water. Panels b and c reproduced with permission under a Creative Commons CC BY 3.0 license from ref 462. Copyright 2016 Royal Chemical Society. (d) Schematic diagram of synthesis CsPbBr₃ NCs into dense SiO₂ by high-temperature solid-state reaction. (e) Photostabilities of the CsPbBr₃–SiO₂, ceramic Sr₂SiO₄:Eu²⁺ green phosphor, KSF red phosphor, colloidal CsPbBr₃ NCs, and CdSe/CdS/ZnS NCs under illumination, sealed with Norland-61 on the LED chips (20 mA, 2.7 V). (f) aged at 85 °C and 85% humidity conditions on the LED chips (20 mA, 2.7 V). Panels d–f are reproduced with permission from ref 283. Reprinted with permission under a Creative Commons CC BY license. Copyright 2020 The Authors. (g) Schematics of encapsulation of CsPbBr₃ NCs into a PVP matrix resulting in water-resistant composites used for the intracellular imaging. Reproduced with permission from ref 442. Copyright 2017 John Wiley & Sons, Inc. (h) Schematics of one-pot synthesis of CsPbBr₃-in-Cs₄PbBr₆ microcrystals from CsBr and PbBr₂ precursors. (i) Crystal structure model for composites synthesized in (h), with a Cs₄PbBr₆ microcrystal in a rhombic prism shape hosting several CsPbBr₃ NCs. (j) SEM image of CsPbBr₃-in-Cs₄PbBr₆ prism-shaped microcrystals. Reproduced with permission from ref 430. Copyright 2017 John Wiley & Sons, Inc.

hostile environments.^{480–482} The tunable size and shape of the pores in MOFs and the ability to modify their surface through functional groups enabled their use as smart materials in anti-counterfeiting applications.^{483,484} For instance, Zhang *et al.*⁴⁸⁴ demonstrated that the PL of MAPbBr₃ perovskite NCs in the pores of MOFs can be reversibly switchable (quenched and recovered) by treatment with water and MABr, and thus this process can be used for multiple encryption and decryption of information.

Furthermore, metal-halide salts have been shown to be able to serve as a protective matrix for improving the chemical stability of perovskite NCs,^{485,486} which was inspired from the original work of Eychmüller and co-authors on protecting conventional QDs through the use of such kind of salt matrices.^{487–489} Dirin *et al.* reported a two-step synthesis, in which first nucleation followed by a shelling process to deposit inorganic NaBr shells around multiple CsPbBr₃ NCs.⁴⁹⁰ Perovskite precursors firstly crystallized on the surface of

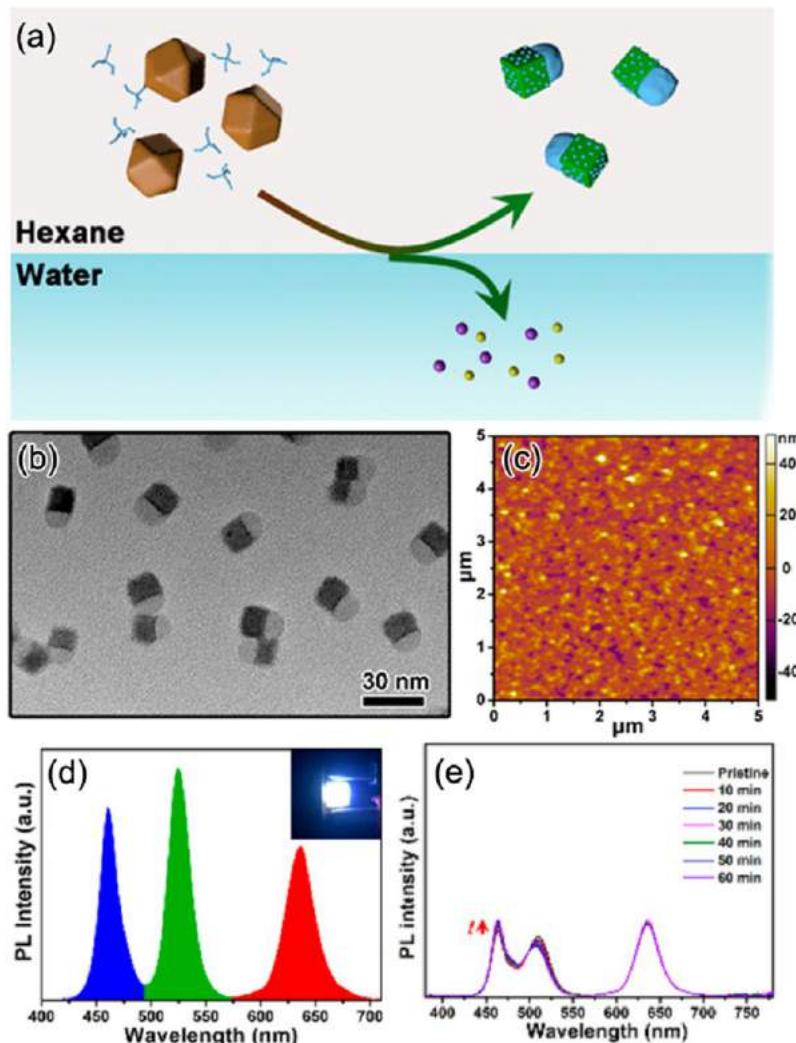


Figure 46. (a) Schematic illustration of the formation of $\text{CsPbX}_3/\text{SiO}_2$ Janus nanoparticles. (b) TEM image of $\text{CsPbBr}_3/\text{SiO}_2$ Janus NCs. (c) AFM image of the film fabricated from the $\text{CsPbBr}_3/\text{SiO}_2$ nanoparticles. (d) PL spectra of $\text{CsPbBr}_3/\text{SiO}_2$ -based WLED device and (e) its corresponding time-dependent PL spectra. Inset in (d) shows an operating device. Reproduced from ref 495. Copyright 2017 American Chemical Society.

microsized alkali halides, followed by a coating process driven by surface reaction of amphiphilic Na and Br precursors in nonpolar solvents. A series of other alkali halides including MgX_2 , CaX_2 , SrX_2 , BaX_2 , and ZnX_2 were tested as well to validate the general applicability of this method.⁴⁹⁰

The combinations of two different semiconductor materials to form core/shell heterostructures have been widely demonstrated for different II–VI, IV–VI, and III–V QDs, where the trap states could be removed and the stability improved.^{67,491} However, the synthetic strategies used for those QDs were not easy to be translated toward lead-halide perovskite NCs, eventually due to their more dynamic surface and lower melting points. $\text{CsPbX}_3/\text{ZnS}$ QDs with a heterojunction-like structure were reported, yet only a partial decoration of the surface of CsPbX_3 NCs with ZnS has been achieved.⁴⁹² Cs_3PbX_6 is an insulating material with a wide band gap of 3.9 eV,⁴⁹³ and smaller CsPbBr_3 NCs encapsulated inside a Cs_4PbBr_6 matrix were found to preserve high PLQY and thus could be used as optical gain materials in lasers and as emissive layers in LEDs.^{364,430} Figure 45h illustrates a one-pot preparation of Cs_4PbBr_6 -in- CsPbBr_3 composites from suitable precursors in a liquid environment, while Figure 45i shows

lattice alignment of CsPbBr_3 NCs within the Cs_4PbBr_6 matrix; well-faceted Cs_4PbBr_6 -in- CsPbBr_3 microprisms are visualized by SEM image in Figure 45j.⁴³⁰ More recently, Cao *et al.* demonstrated the use of the CsPbX_3 -in- Cs_4PbX_6 composites for X-ray sensing and imaging, with the Cs_4PbBr_6 matrix providing a favorable enhancement in the attenuation of X-rays.⁴⁹⁴

Encapsulation at Single-Particle Level. From the aforementioned encapsulation strategies, a variety of materials including polymers, SiO_2 , and AlO_x have been employed to stabilize CsPbX_3 NCs, resulting in impressive stability improvement. The capsule-like structure endowed CsPbX_3 NCs with enhanced optical properties accompanied by exceptional stability. In these successful encapsulation examples, however, the as-obtained products always had multiple particles in one shell, resulting in large particle size that could reach up to tens of micrometers. In general, the CsPbX_3 NCs used in optoelectronic devices are assembled in the form of a film, in which undesirable large particles would weaken the film quality and consequently corresponding device performance. In addition to the poor uniformity in film, micrometer-sized particles were unfavorable in many bio-

related areas, such as cell uptake. More importantly, the large particle size hampers their solution processability. The straightforward solution for this problem is to shrink the size of the encapsulated CsPbX_3 product down to the nanoscale. Significant efforts have been devoted to exploring the encapsulation of CsPbX_3 NC at single-particle level. Up to now, oxides and semiconductors have been employed in the fabrication of CsPbX_3 -based core/shell nanostructures with significantly improved optical properties and stability.

In 2017, Hu *et al.*⁴⁹⁵ developed a sol-gel method to produce monodispersed $\text{CsPbX}_3/\text{SiO}_2$ Janus NCs at the oil–water interface. The simultaneous transformation $\text{Cs}_4\text{PbX}_6 \rightarrow \text{CsPbX}_3$ and growth of SiO_2 at one side of CsPbX_3 NCs led to the formation of a distinctive Janus structure, as shown in Figure 46a,b. As expected, the modification of SiO_2 ensured CsPbX_3 NCs fewer surface traps and enhanced photophysical properties. More importantly, $\text{CsPbX}_3/\text{SiO}_2$ Janus NCs could be fabricated into a high-quality film, which exhibited comparable smoothness and uniformity to pristine CsPbX_3 NCs, as shown in Figure 46c. In addition, $\text{CsPbBr}_3/\text{SiO}_2$ Janus nanoparticles could be employed as an emitting layer in a WLED, resulting in a significantly improved photostability under continuous UV irradiation (Figure 46d,e).

In comparison with pristine CsPbX_3 NCs, the aforementioned $\text{CsPbX}_3/\text{SiO}_2$ Janus structure achieved great strides in their durability against water and irradiation. The long-term stability remains a challenge because of the partial coverage with oxides. The core/shell structure offers a more promising solution due to the complete encapsulation of CsPbX_3 NCs. SiO_2 ^{496,497} and Al_2O_3 ²⁹¹ shells have been successfully coated on the CsPbX_3 NCs to produce core/shell nanostructures using hydrolysis and atomic layer deposition (ALD), respectively. For example, a modified supersaturated recrystallization approach has been developed to synthesis $\text{CsPbBr}_3/\text{SiO}_2$ core/shell nanostructures, as shown in Figure 47a.⁴⁹⁶ During the whole reaction, the product quality was sensitive to multiple parameters, such as capping ligand type and density, reaction temperature, silica precursor, and ammonia concentration. Therefore, the well-defined core/shell structure could be realized only by carefully controlling the reaction conditions. As a result, monodisperse core/shell nanoparticles with only one CsPbBr_3 core encapsulated in one SiO_2 shell were obtained (Figure 47b), which displayed outstanding stability against water under ultrasonication treatment, as shown in Figure 47c. Later, a reverse microemulsion method was developed to prepare of SiO_2 shell-coated Mn^{2+} -doped $\text{CsPbCl}_{x}\text{Br}_{3-x}$ NCs by incorporation of the multibranched capping ligand TOPO.⁴⁹⁷ One typical feature of this product was its ultrathin SiO_2 shell, which ensured not only improved stability but also excellent optical properties. Another method in the preparation of ultrathin inert shell was the colloidal ALD reported by Loidice *et al.*²⁹¹ The resulting $\text{CsPbX}_3/\text{AlO}_x$ core/shell nanoparticles preserved the colloidal stability of CsPbX_3 NCs and it was possible to control the thickness of the AlO_x shell from 1 to 6 nm. For inert shell encapsulation, the product always exhibited improved photophysical features and enhanced stability compared to naked CsPbX_3 NCs. However, the inert shell would weaken the electrical properties, resulting in a poor performance in photoelectric devices such as solar cells and electroluminescent LEDs. It may provide more possibilities in practical applications if one can further reduce the inert shell thickness or employ another semiconductor material to encapsulate CsPbX_3 NCs.

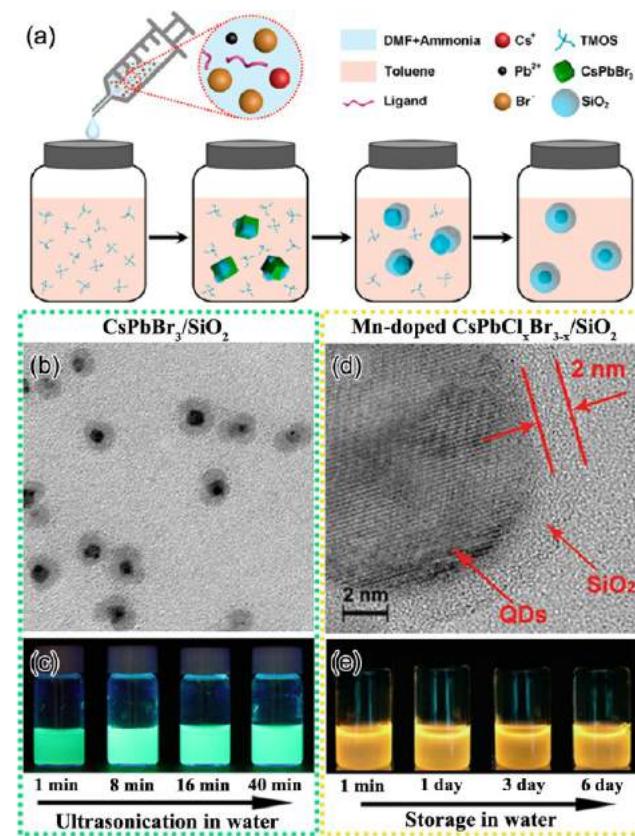


Figure 47. (a) Formation mechanism of $\text{CsPbBr}_3/\text{SiO}_2$ core/shell NCs. (b) TEM image and (c) photographs of $\text{CsPbBr}_3/\text{SiO}_2$ NCs showing the durability against water under ultrasonication. Panels a–c reproduced from ref 496. Copyright 2018 American Chemical Society. (d) TEM image and (e) photographs of Mn^{2+} -doped $\text{CsPbCl}_{x}\text{Br}_{3-x}/\text{SiO}_2$ core/shell nanoparticles against water. Panels d and e reproduced with permission from ref 497. Copyright 2019 John Wiley & Sons, Inc.

Inspired by the core/shell structure in traditional II–VI (e.g., CdSe/ZnS) quantum dots,^{122,498} a variety of semiconductors have been exploited for the synthesis of CsPbX_3 -based heterojunction. In most cases, Cs_4PbX_6 is usually employed as the shell composition to enhance CsPbX_3 performance in photophysical characteristics and durability.^{364,417,430,450,452} It may be ascribed to the similar ternary crystal structure and identical $[\text{PbX}_6]^{4-}$ units in both CsPbX_3 and Cs_4PbX_6 , which makes the corresponding dual-phase composite stable. In the bulk phase and multi-nanoparticle coating, CsPbX_3 embedded in Cs_4PbX_6 host achieves an enhancement in both PLQY and stability compared to the pristine CsPbX_3 . Only limited investigations, however, have been reported in the single-particle encapsulation. A seed-mediated approach has been established in the synthesis of $\text{CsPbBr}_3/\text{Cs}_4\text{PbBr}_6$ core/shell NCs.⁴⁹⁹ In a typical process, additional cesium and halide precursors were introduced into as-prepared CsPbBr_3 NC solution under certain conditions, resulting in hexagonal Cs_4PbBr_6 shell formation on the CsPbBr_3 surface. The distinctive core/shell heterostructure consisted of a core with narrow band gap and a shell with a large band gap, resulting in a type-I band alignment, in which CB and VB of the core were located within those of the shell (Figure 48a). Consequently, the excited carriers could be well-confined within the CsPbX_3 core and gave rise to an enhanced recombination rate and

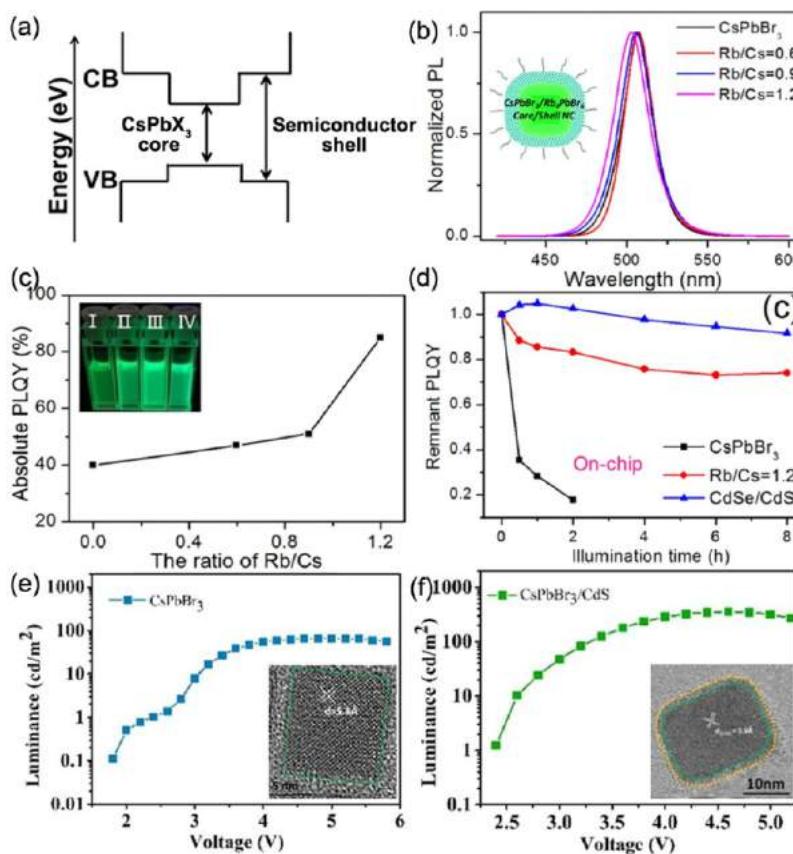


Figure 48. (a) Band alignment of type-I composite with core/shell structure. (b) PL spectra, (c) PLQY, and (d) photostability of naked CsPbBr_3 and $\text{CsPbBr}_3/\text{Rb}_4\text{PbBr}_6$ core/shell NCs. Insets in (c) show the images of CsPbBr_3 NCs with/without Rb treatment under 365 nm lamp: I, CsPbBr_3 ; II, $\text{Rb}/\text{Cs} = 0.6$; III, $\text{Rb}/\text{Cs} = 0.9$; IV, $\text{Rb}/\text{Cs} = 1.2$. Panels a–d are reproduced from ref 301. Copyright 2018 American Chemical Society. L–V curves of (e) CsPbBr_3 and (f) $\text{CsPbBr}_3/\text{CdS}$ core/shell NCs. Insets in (e) and (f) show TEM images of CsPbBr_3 and $\text{CsPbBr}_3/\text{CdS}$ NC. Panels e and f are reproduced with permission under a Creative Common CC-BY license from ref 501. Copyright 2019 Frontiers.

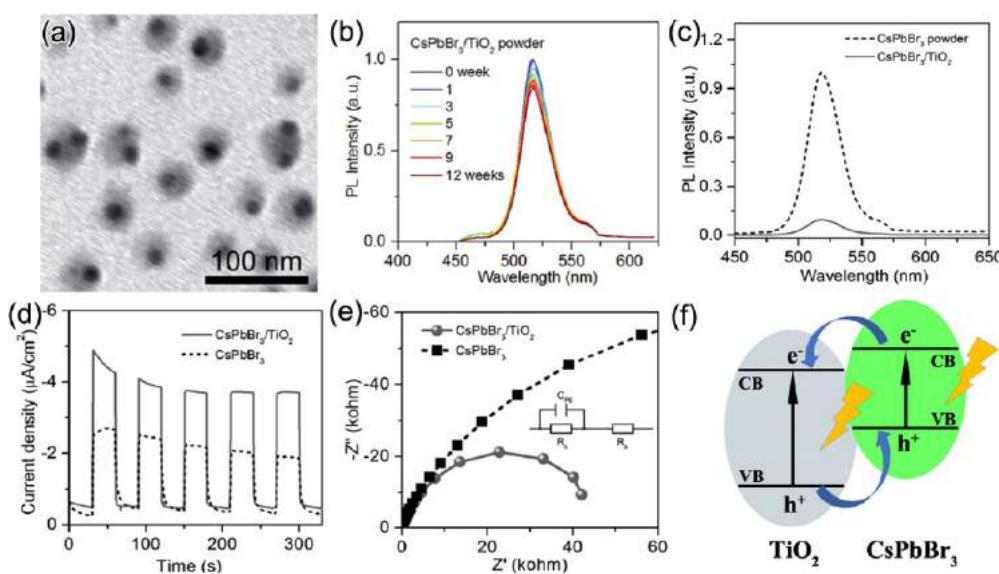


Figure 49. (a) TEM image of $\text{CsPbBr}_3/\text{TiO}_2$ core/shell NCs. (b) Relative PL intensity of $\text{CsPbBr}_3/\text{TiO}_2$ NCs in water. (c) PL spectra, (d) transient photocurrent responses, and (e) Nyquist plot of CsPbBr_3 and $\text{CsPbBr}_3/\text{TiO}_2$. Panels a–e reproduced with permission from ref 365. Copyright 2017 John Wiley & Sons, Inc. (f) Band alignment within this type-II heterostructure.

PLQY. In parallel to Cs_4PbX_6 , also CsPb_2X_5 , with its large band gap, has been exploited in the fabrication of type-I heterostructures, this time containing a CsPbX_3 core and a

CsPb_2X_5 shell, again with the purpose to optimize the optical features.^{443,500}

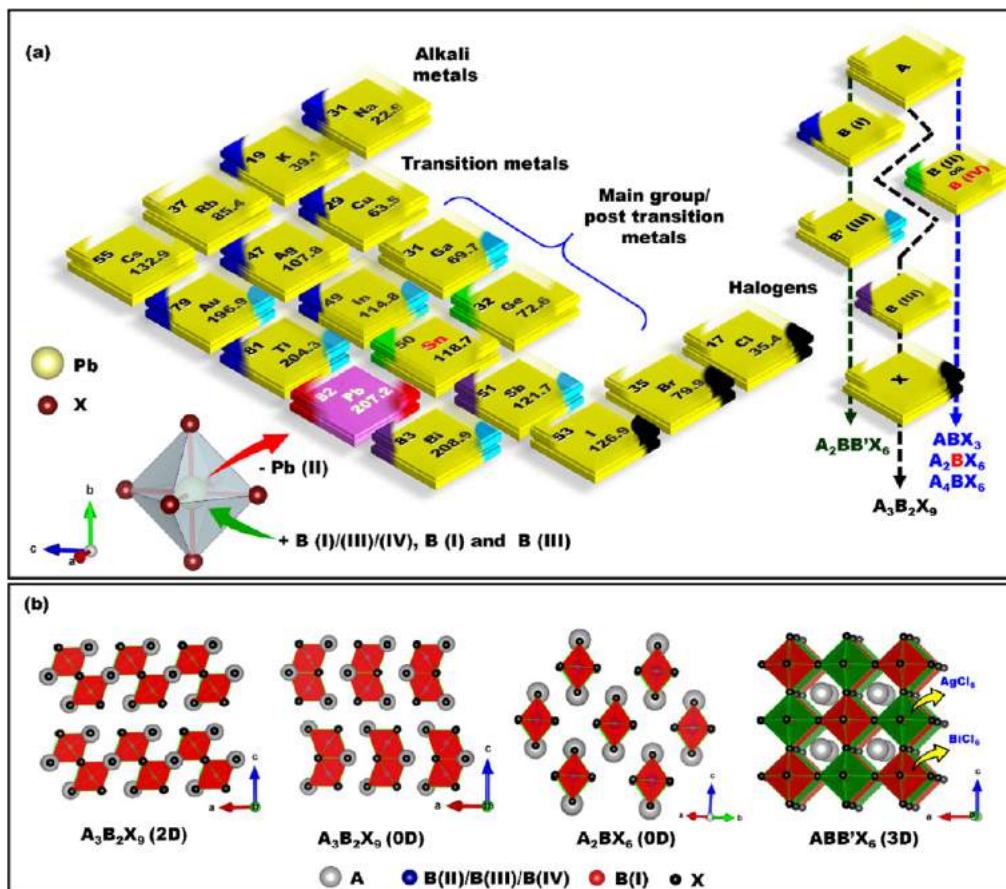


Figure 50. (a) Combinations of elements from a part of periodic table forming possible Pb-free metal-halide perovskite and their derivative structures. The triangular color code specifies the site occupancy as per the compositional formula presented in the extreme right. (b) Structural presentation of Pb-free metal-halide perovskites and perovskite derivatives showing network of octahedra in 3D, 2D, and 0D directions.

In addition to $Cs_xPb_yX_z$ shell growth, Rb_4PbX_6 and II–VI semiconductors might be suitable shell materials for $CsPbX_3$ NCs to fabricate type-I or quasi-type-I structures. For example, a post-synthesis phase transformation $CsPbBr_3$ NC \rightarrow $CsPbBr_3/Rb_4PbBr_6$ core/shell nanostructure was presented by reacting $CsPbBr_3$ NCs with rubidium oleate (also discussed in [Composition Control by Ion Exchange and Suppression of Exchange](#) section).³⁰¹ By controlling the Rb/Cs ratio in the precursor, it was possible to regulate the thickness of the Rb_4PbBr_6 shell, resulting in an obvious blue shift in PL emission and increasing absolute PLQY, as shown in [Figure 48b,c](#). More importantly, the core/shell hybrid showed significantly enhanced photostability after a long-term operation, which was comparable to the $CdSe/CdS$ core/shell quantum dots ([Figure 48d](#)). Very recently, a II–VI semiconductor CdS shell was found to efficiently suppress the nonradiative recombination of $CsPbX_3$ NCs due to the type-I alignment.³⁰¹ In addition, the CdS layer effectively passivates the surface traps, leading to a higher radiative recombination rate. Notably, an inverted LED (ITO/ZnO:Mg/QDs/CBP-(4,4'-bis(*N*-carbazolyl)-1,1'-biphenyl)/ MoO_3 /Al) was fabricated based on the $CsPbBr_3/CdS$ core/shell heterostructure. A maximum luminance of 354 cd/m² was measured for $CsPbBr_3/CdS$ NCs, whereas a value of only 65 cd/m² was measured for pure $CsPbBr_3$ nanoparticles. The average EQE was 0.4 and 0.07% for the core/shell and naked samples, respectively. Though the overall performance of core/shell

heterostructure is moderate, it sheds some light on future directions in the modification of $CsPbX_3$ NCs.

By tuning the composite components, one can easily adjust the energy or charge-transfer process.⁴²⁷ For example, type-II composites could be fabricated using TiO_2 shell to encapsulate $CsPbBr_3$.³⁰⁵ Similar to inert shell coating, the resulting product exhibited a well-defined core/shell nanostructure and excellent stability in water, as shown in [Figure 49a,b](#). However, its PL emission demonstrated an obviously quenching compared to naked $CsPbBr_3$ NCs ([Figure 49c](#)). Moreover, photoelectrochemical studies including transient photocurrent responses and Nyquist plots suggested an increased charge separation efficiency of $CsPbBr_3$ NCs upon TiO_2 shell encapsulation ([Figure 49d,e](#)). In strong contrast to the aforementioned type-I composite, photoinduced charges were effectively separated and accumulated in the TiO_2 and $CsPbBr_3$ components, respectively, and this might facilitate photocatalytic reactions.

NANOCRYSTALS OF LEAD-FREE PEROVSKITE-INSPIRED MATERIALS

Despite rapid advancements in the synthesis, understanding and performance of Pb-based perovskite NCs, the toxicity of Pb and the soluble nature of the Pb-based compounds in polar solvents remain an issue for their widespread application. This is related to the fact that the lead content in electronic products is restricted to 0.1 wt % by the Regulation of Hazardous Substances. This lead content restriction is as per

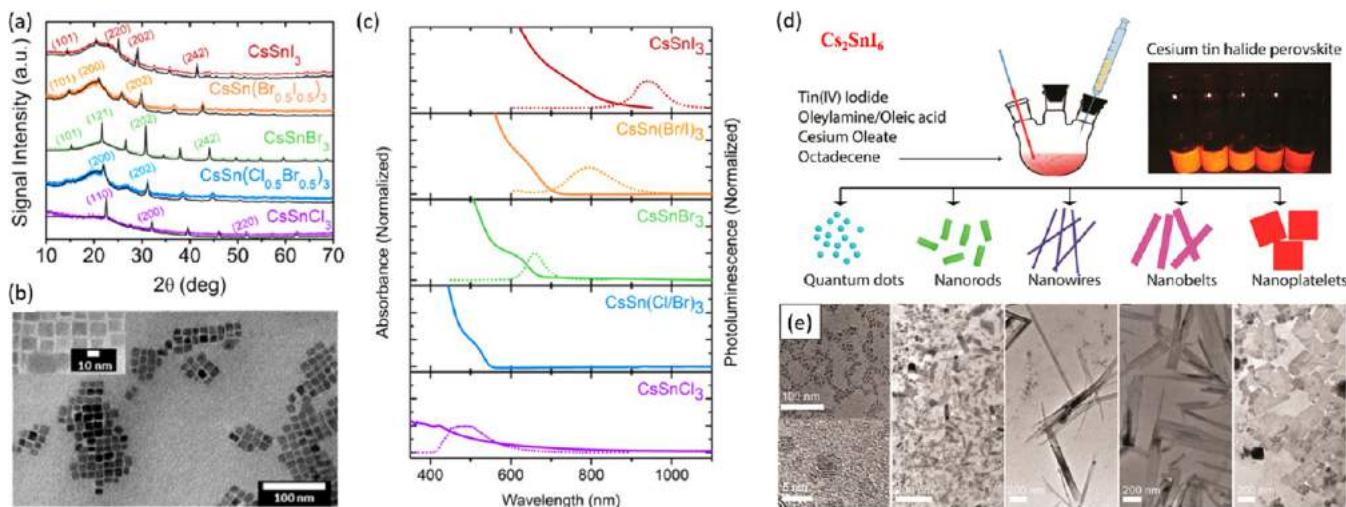


Figure 51. (a) XRD pattern of CsSnX_3 ($\text{X} = \text{Cl}, \text{Cl}_{0.5}\text{Br}_{0.5}, \text{Br}, \text{Br}_{0.5}\text{I}_{0.5}, \text{I}$) perovskite NCs synthesized by the hot-injection method. (b) TEM images and (c) UV-vis–NIR absorbance and PL spectra of CsSnX_3 NCs of different halide compositions. (d) Schematic illustration of the synthesis of Cs_2SnI_6 perovskite NCs by the hot-injection approach (left panel) and photograph of the prepared colloidal solutions of Cs_2SnI_6 NCs under UV light (right panel). (e) Corresponding TEM images of the Cs_2SnI_6 NCs of different morphologies. Panels a–c are reprinted under a Creative Commons CC-BY License from ref 515. Copyright 2016 American Chemical Society. Further permissions related to the material excerpted should be directed to the ACS. Panels d and e are adapted from ref 522. Copyright 2016 American Chemical Society.

the European Union guidelines and may vary in other jurisdictions.⁵⁰² This practical consideration demands for environmentally benign metal-halide perovskites. Furthermore, there is the fundamental question on whether we could identify alternative classes of materials that could replicate the exceptional optoelectronic properties of the Pb-halide perovskites. Both factors have motivated researchers across the globe to undertake extensive theoretical and experimental work for designing Pb-free metal-halide perovskites. In this subsection, we will highlight the major progress of the field, with emphasis on colloidal NC systems. Readers may also refer to prior review articles on Pb-free perovskite NCs.^{102,109,114,503–507} In the present article, we will capture the recent developments and insights into Pb-free metal-halide perovskite NCs. In addition to materials with perovskite crystal structures, we will also discuss perovskite derivatives that are chemically or electronically analogous to MHPs, but do not have a perovskite structure.

Lead-Free Perovskites and Their Derivatives. Colloidal Synthesis and Optical Properties. Figure 50a shows a selection of elements from the periodic table that are presently being considered as substitutes for Pb(II). The color code specifies the B-site occupancy in composition presented at the extreme right in Figure 50a. The crystal structures of representative generic compositions for which colloidal NCs have already been prepared are given in Figure 50b. Substituting Pb(II) with other group 14 elements (e.g., Sn(II) and Ge(II)) maintains the perovskite crystal structure (i.e., ABX_3). On the other hand, substituting Pb(II) with an element from group 15 will result in materials with the $\text{A}_3\text{B}_2\text{X}_9$ stoichiometry, and these materials could either take on a 2D or 0D crystal structure (Figure 50b). To maintain the cubic perovskite crystal structure, the B-site in ABX_3 compounds could be alternately substituted for group 13 (e.g., Ag(I)) and group 15 (e.g., Bi(III)) elements. This results in double perovskite materials with the generic formula $\text{A}_2\text{B}(\text{I})\text{B}'(\text{III})\text{X}_6$. One can go further and replace the B'-site with a tetravalent cation (e.g., Sn^{4+} or Ti^{4+}). In order to maintain charge

neutrality in a perovskite crystal structure, the B-site would need to be vacant. This, therefore, results in the vacancy-ordered double perovskites, with the generic formula A_2BX_6 .

Sn- and Ge-Based Perovskite and Perovskite Derivative NCs. The direct substitution of Pb(II) with an isovalent element to maintain the ABX_3 crystal structure has been one of the earliest manifestations of lead-free perovskite derivatives. Sn- and Ge-based perovskites have been successfully demonstrated in bulk thin films, both in hybrid and all-inorganic structures.^{508–514} Colloidal synthesis of CsSnX_3 NCs with different sizes and shapes has also been reported, along with the tuning of the optical properties.^{500,515–517} The band gap of CsSnX_3 perovskite is lower compared to the analogues Pb²⁺-based MHP mostly due to higher electronegativity of Sn ions compared to Pb.^{515,518} Huang *et al.* showed that the relatively small band gap changes from CsSnCl_3 to CsSnI_3 are due to interatomic Sn s and Sn p character of the VBM and the conduction band minima (CBM), respectively.⁵¹⁹ This leads to high oscillator strength in these direct band gap perovskites where the photoluminescence peak was assigned to acceptor bound excitons.⁵¹⁹

The methods for synthesizing lead-free perovskite NCs are essentially the same as those used for the synthesis of lead-halide NCs discussed in earlier sections. The synthesis of CsSnX_3 NCs were initially reported by Jellicoe *et al.*, who prepared the colloidal NC solution by hot injection (Figure 51a–c).⁵¹⁵ The CsSnCl_3 NCs have a perovskite crystal structure with a cubic space group ($\text{Pm}\bar{3}m$), while the CsSnBr_3 and CsSnI_3 NCs have a lower symmetry orthorhombic (Pnma) phase (Figure 51a).⁵¹⁵ The synthesized CsSnX_3 nanocubes were nearly monodisperse, with a size of 10 nm, and their band gap could be easily tuned over the visible and near-infrared (NIR) range by changing the halide ($\text{X} = \text{Cl}, \text{Br}$, and I) composition (Figure 51a,b). The CsSnX_3 NCs exhibit red-shifted emission (lower band gap) compared to corresponding CsPbX_3 NCs with the same size and halide. Beyond composition, the band gap of CsSnX_3 NCs could also be tuned through their size and dimensionality.^{515,516} For

instance, Wong *et al.*⁵¹⁶ demonstrated the synthesis of strongly quantum-confined CsSnI_3 NPs with blue-shifted PL (1.59 eV) compared to the PL in bulk (1.3 eV). Computations also predicted that CsSnI_3 NPs synthesized under Sn-rich conditions would have lower defect densities and higher stability.⁵¹⁶ In general, 2D-layered perovskites have been reported to exhibit higher stability over their bulk counterparts.⁵²⁰ The high density of surface ligands protects 2D-layered perovskites or NPs from air and moisture. It has been shown that Sn-based colloidal 2D perovskite NPs can be easily prepared at room temperature by ligand-assisted nonsolvent crystallization method.²⁰⁹

Despite successful shape-controlled synthesis of CsSnX_3 NCs, the stability of these NCs is still a major concern. This is a consequence of the fact that, when these NCs are exposed to ambient conditions, Sn^{2+} quickly oxidizes to Sn^{4+} , forming a different composition, Cs_2SnX_6 ,⁵¹⁵ which has a 0D crystal structure, as shown in Figure 50.^{521–525} Several reports have indicated trioctyl phosphine ligands to be promising for stabilizing CsSnX_3 NCs. However, the transformation of Sn(II) to Sn(IV) over time is inevitable.^{515,516} The morphology of perovskite NCs can have an influence on their stability. For instance, Wang *et al.*⁵²⁶ demonstrated that CsSnBr_3 cubic nanocages exhibit improved stability under ambient conditions. These nanocages were synthesized by hot injection using stannous 2-ethylhexanoate (instead of TOP- SnBr_2) as the Sn precursor and MgBr_2 as the bromide precursor. Importantly, the surface treatment of CsSnBr_3 nanocages with perfluoroctanoic acid (PFOA) can significantly improve their stability against moisture, light and oxygen. This was attributed to the strongly electronegative F-groups in PFOA suppressing the oxidation of Sn^{2+} to Sn^{4+} , whereas the bulky carbon chain prevented O_2 and H_2O access to the perovskite through steric hindrance.⁵²⁶ The stability of Sn-perovskites could also be improved through the formation of multication alloying at the A- or B-site.^{527,528} Several attempts have also been made to improve the structural and environmental stability by only partially replacing Pb with Sn.^{529,530} Such $\text{CsPb}_x\text{Sn}_{1-x}\text{X}_3$ NCs can be obtained either through ion exchange or *via* direct synthesis.^{528,530} These $\text{CsPb}_x\text{Sn}_{1-x}\text{X}_3$ NCs were found to be stable for months in ambient conditions and have been successfully used in the fabrication of perovskite NC-based solar cells⁵³⁰ and LEDs.⁵³¹ However, NCs showed poor performance as compared to the polycrystalline films due to the large number of grain boundaries and surface ligands which retard charge transport.⁵³² The environmental and thermal stability were also improved by mixing Cs with MA in the A-site (*i.e.* $\text{MA}_{0.5}\text{Cs}_{0.5}\text{Pb}_{1-x}\text{Sn}_x\text{Br}_3$) *via* the LARP approach.⁵³³

Although significant progress has been made toward the improvement of the phase stability of Sn-based perovskite NCs, it is still far from reaching the stability and optical quality of Pb-based perovskite NCs. On the other hand, groups have taken advantage of the improved stability of Sn(IV) over Sn(II) to synthesize stable and optically emissive Cs_2SnI_6 NCs (Figure 51d).^{522,534,535} These NCs can be prepared by conventional hot injection using oleylamine and oleic acid as ligands.⁵²² The shape of the Cs_2SnI_6 NCs is easily controllable from spherical dots to nanorods and nanowires, and nanobelts to nanoplatelets (Figure 51e). In addition, these NCs can also be synthesized *via* hot injection without the use of capping ligands, as demonstrated by Weiss and co-workers. In this ligand-free approach, the size of the Cs_2SnI_6 NCs (from 12 ± 3

to 38 ± 4 nm) and thus their band gap is tunable by controlling the reaction temperature. Since these NCs are ligand-free, it is easy to process them into high-quality thick NC films by simple drop-casting, and these films could be promising for optoelectronic applications.⁵³⁴

On the other hand, unlike Sn-perovskite NCs, only a few attempts have been made to synthesize Ge-perovskite NCs.^{536–538} In general, the synthesis of Ge-perovskite NCs needs to be carried out under an inert atmosphere due to the ready oxidation of Ge(II) to Ge(IV). The instability of Ge(II) is a critical limitation with this class of materials. It has been demonstrated that monodisperse CsGeI_3 NCs can be prepared by hot injection under an inert atmosphere.⁵³⁶ However, the NCs are highly sensitive to electron beam irradiation and they initially transform into CsI single crystals and eventually fragment into randomly oriented small debris. Moreover, CsGeX_3 (X = Cl, Br, and I) nanorods with tunable optical properties were prepared by solvothermal synthesis, and the solar cells made of CsGeI_3 NCs exhibit PCE of 4.92%.⁵³⁸ Despite these few studies, the shape-controlled synthesis and application of CsGeX_3 NCs are largely unexplored. Further efforts are needed in this direction, because these NCs might be promising for solar cells due to their low band gap as compared to Sn- and Pb-based perovskites. Ge-based perovskites have also been synthesized as quantum rods (QRs).⁵³⁸ The optical band-edge of CsGeX_3 quantum rods contains sharp absorption peak where the corresponding absorption onset shows a 90 nm red shift from 565 to 655 nm while going from CsGeCl_3 to CsGeI_3 . The PL peak of these QRs tuned from 607 to 696 nm with a fwhm of about 25 nm.⁵³⁸

Beyond Ge-based perovskites, Eu^{2+} and Yb^{2+} have also been used in the B-site.^{523,539} CsEuCl_3 NCs exhibit strong excitonic absorption at ~ 350 nm, with a Stokes-shifted PL at 435 nm. The PL peak has a narrow fwhm of 19 nm. Interestingly, in order to overcome the $\text{Eu}^{2+} \rightarrow \text{Eu}^{3+}$ oxidation, EuCl_3 was used and reduced to Eu^{2+} by oleylamine prior to the injection of Cs-oleate.⁵²³ Moon *et al.*⁵³⁹ demonstrated the synthesis of monodisperse CsPbI_3 NCs by hot injection, with a size of 10 ± 1 nm. These NCs have a low exciton binding energy of 33 meV, suggesting that excitons are readily dissociated at room temperature. The PL peak is Stokes shifted by only 7 nm to the absorption edge, and the PLQY is a high value of 58%. These materials achieved a high photoresponsivity reaching 2.4×10^3 A W⁻¹ in photodetectors.⁵³⁹

Bi-, Sb-, and Tl-Based Perovskite Derivative NCs. Next we discuss materials with trivalent B-site cations, namely, Bi(III) and Sb(III). The fact that both Bi(III) and Sb(III) have valence s^2 electrons, similar to Pb(II), encouraged researchers to explore Bi- and Sb-halide perovskite-derivative NCs.^{503,540–547} However, bismuth and antimony are stable in the +3 oxidation state, whereas lead forms a stable +2 oxidation state. So, two B(III) (B = Sb or Bi) cations replace three Pb(II) ions in $\text{A}_3\text{Pb}_3\text{X}_9$ (or APbX_3), forming compounds with the general formula $\text{A}_3\text{B}_2\text{X}_9$ (Figure 50). Consequently, the 3D perovskite structure of APbX_3 is lost, resulting in compounds with a 2D (*e.g.*, $\text{Rb}_3\text{Sb}_2\text{I}_9$) or 0D structure (*e.g.*, $\text{Cs}_3\text{Bi}_2\text{I}_9$).^{97,548} The incorporation of smaller cations such as Rb as the A-site cation in place of the Cs, the layered phase is favorable over the dimer phase, and thus this favors the growth of 2D $\text{Rb}_3\text{Sb}_2\text{I}_9$ structures. For instance, Sargent and co-workers reported the synthesis of $\text{Rb}_3\text{Sb}_2\text{I}_9$ nanoplatelets and single crystals. Interestingly, they found that the nanoplatelets exhibit narrow emission (fwhm = 21 nm) with PL peak

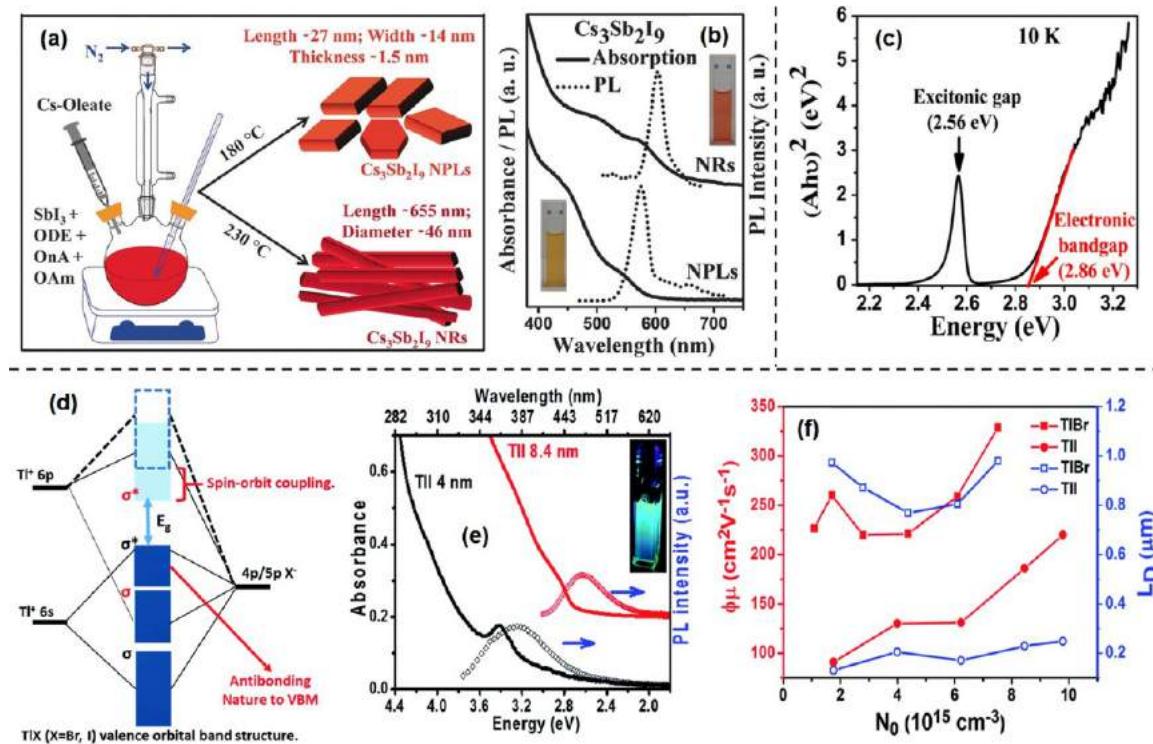


Figure 52. (a) Schematic showing colloidal synthesis of $\text{Cs}_3\text{Sb}_2\text{I}_9$ nanoplatelets and nanorods. ODE, OnA, and OLA are abbreviated forms of 1-octadecene, octanoic acid, and oleylamine, respectively. (b) Optical absorption and emission spectra of colloidal $\text{Cs}_3\text{Sb}_2\text{I}_9$ NPLs and NRs. Photographs shown in the inset are of colloidal $\text{Cs}_3\text{Sb}_2\text{I}_9$ NPLs (yellow) and NRs (red) under visible light. (c) Tauc plot of $\text{Cs}_3\text{Bi}_2\text{I}_9$ NCs obtained from optical absorption data measured at 10 K. (d) Schematic illustration of the valence orbital band structure of $\text{TI}X$ ($X = \text{Br}$ and I). Dark blue color corresponds to bonding and antibonding orbitals formed by hybridization of p and s atomic orbitals of TI^+ and X^- . (e) Optical absorption and emission spectra of TII NCs. Photograph in the inset shows colloidal dispersion of 8.4 nm TII NCs under 365 nm UV light. (f) Comparison of effective carrier mobility ($\phi\mu$, red) and carrier diffusion length (L_D , blue) of films of TIBr (28.7 nm) and TII (8.4 nm) NCs, obtained using terahertz spectroscopy. N_0 is carrier density obtained at a given excitation fluence. Panels a and b are adapted with permission from ref 544. Copyright 2017 John Wiley and Sons. Panel c is adapted from ref 545. Copyright 2018 American Chemical Society. Panels d–f are adapted with permission under a Creative Commons CC BY 3.0 license from ref 554. Copyright 2017 Royal Society of Chemistry.

centred 512 nm, while the single crystals exhibit broad emission (fwhm = 75 nm) at 635 nm.⁵⁴⁸ There are multiple reports of the synthesis of colloidal $\text{Cs}_2\text{Sb}_3\text{I}_3$ and $\text{Cs}_2\text{Sb}_3\text{Br}_3$ NCs.^{544,549,550} Schematics in Figure 52a shows a typical hot-injection synthesis method for forming nanoplatelets and nanorods of $\text{Cs}_3\text{Sb}_2\text{I}_9$ under different reaction conditions.⁵⁴⁴

Figure 52b shows the corresponding UV-visible absorption and photoluminescence spectra. Colloidal dispersion, band-edge emission, and quantum-confinement effects are observed in $\text{Cs}_3\text{Sb}_2\text{I}_9$ NCs. Figure 52c reports the UV-visible absorption spectra (Tauc plot) of $\text{Cs}_3\text{Sb}_2\text{I}_9$ NCs at 10 K.⁵⁴⁵ Owing to its 0D structure, $\text{Cs}_3\text{Bi}_2\text{I}_9$ shows a high exciton binding energy of ~300 meV, clearly separating the excitonic absorption peak from the band-edge. Reduction of structural dimensionality from 3D to 2D to 0D typically decreases carrier mobility and increases band gap. Therefore, Sb- and Bi-halide perovskite derivatives show inferior photovoltaic properties compared to Pb-halide perovskites. Instead, one can think of other applications such as light-emitting diodes and surface-enhanced Raman spectroscopy using $\text{Cs}_3\text{Sb}_2\text{X}_9$ and $\text{Cs}_3\text{Bi}_2\text{X}_9$ NCs.^{550–552} However, further increases in PLQY by optimizing the defect chemistry is required. Interestingly, Leng *et al.*⁵³⁶ reported that Cl-passivation boost the blue photoluminescence of $\text{MA}_3\text{Bi}_2\text{Br}_9$ NCs up to a PLQY of 54.1%, which is high compared to other lead-free perovskite or perovskite-derivative NCs. Similarly, high PLQYs of 62% and

22% were reported for $\text{Cs}_3\text{Bi}_2\text{Cl}_9$ and $\text{Cs}_3\text{Bi}_2\text{Br}_9$, respectively, using a mixture of octylammonium bromide and oleic acid as ligands.⁵⁵³ These high PLQYs were attributed to the effective passivation of surface traps through strong ligand binding. These perovskite derivative NCs are therefore promising for further exploration.

We would like to mention here about another interesting class of materials, namely, $\text{TI}X$ ($X = \text{Br}, \text{I}$). $\text{TI}X$ does not have a perovskite crystal structure. However, (i) $\text{TI}(\text{I})$ is isoelectronic with $\text{Pb}(\text{II})$ with $6s^2$ valence electrons, and (ii) the electronic structure of $\text{TI}X$ is similar to that of CsPbX_3 . The electronic structure of $\text{TI}X$ is similar to the Pb-halide perovskites, in which the valence band is composed of cation 6s halide 5 p orbitals and the conduction band is composed of cation 6p and halide 5p orbitals (Figure 52d). This motivated Mir *et al.* to synthesize colloidal $\text{TI}X$ NCs.⁵⁵⁴ Figure 52e compares optical absorption and emission of TII NCs with two different sizes. TIBr and TII NCs emit UV-blue light with ~10% PLQY, which is reasonable compared to chloride-based perovskites emitting in the UV-blue range. Notable carrier mobilities and carrier diffusion lengths (L_D) of TIBr (28.7 nm) and TII (8.4 nm) NCs estimated by terahertz spectroscopy are shown in Figure 52f. Such high values of intrinsic carrier mobility, diffusion length, and PLQY suggest that $\text{TI}X$ NCs can be a good optoelectronic material in the UV-blue region. On the other

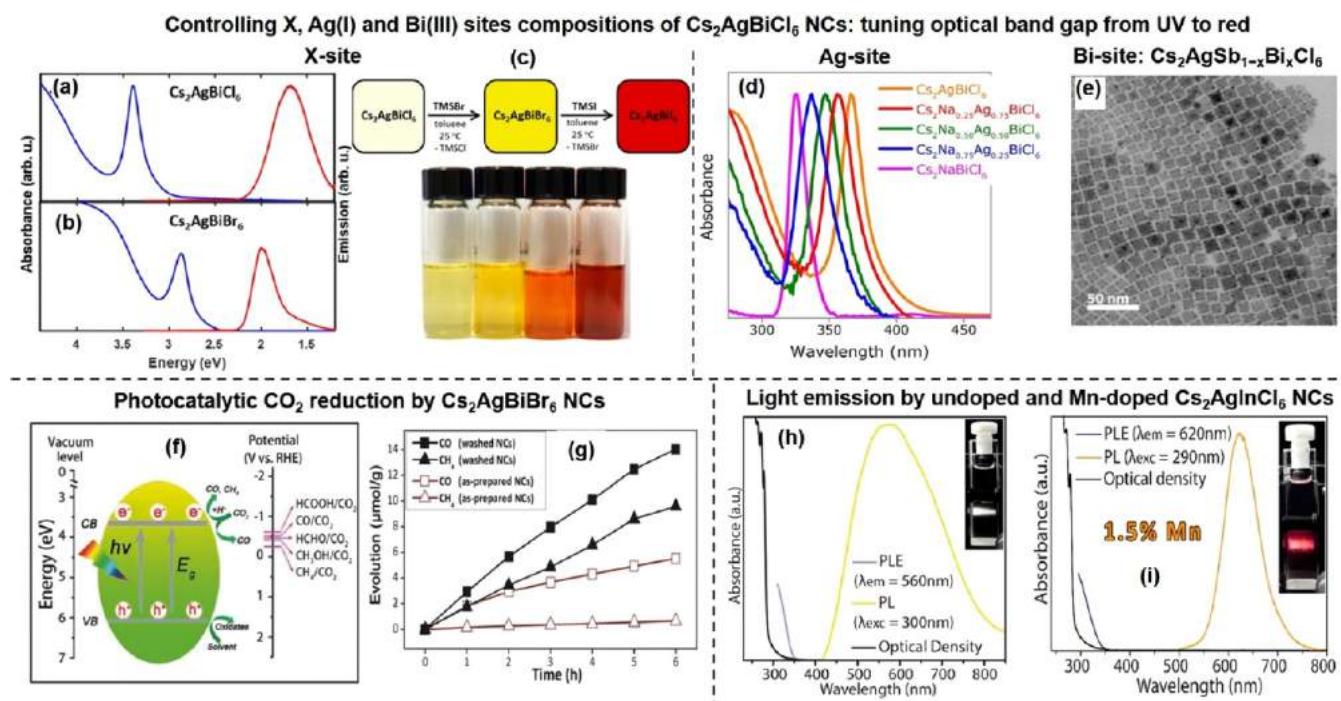


Figure 53. UV-vis absorption spectra (blue) measured at room temperature and PL spectra (red) measured at 20 K for (a) $\text{Cs}_2\text{AgBiCl}_6$ NCs (NCs) and (b) $\text{Cs}_2\text{AgBiBr}_6$ NCs. (c) Scheme showing halide exchange reactions using trimethylsilyl halide (TMSBr or TMSI) and photographs (left to right) show colloidal dispersions of $\text{Cs}_2\text{AgBiBr}_6$, $\text{Cs}_2\text{AgBiBr}_{5.2}\text{I}_{0.8}$, $\text{Cs}_2\text{AgBiBr}_{1.6}\text{I}_{4.4}$, and $\text{Cs}_2\text{AgBiI}_6$ NCs under visible white light. (d) UV-vis absorption spectra of Na alloyed $\text{Cs}_2\text{AgBiCl}_6$ NCs showing shift toward higher energy with increasing Na. (e) Transmission electron microscopy image of $\text{Cs}_2\text{AgSb}_{0.30}\text{Bi}_{0.70}\text{Cl}_6$ NCs. (f) Schematic showing mechanism of photocatalytic CO_2 reduction on the surface of $\text{Cs}_2\text{AgBiBr}_6$ NCs. (g) Plot of CO and CH_4 evolution with respect to time upon photocatalytic CO_2 reduction using as-prepared (red) and washed (black) $\text{Cs}_2\text{AgBiBr}_6$ NCs. UV-vis absorption, PL, and PL excitation (PLE) spectra of (h) undoped and (i) Mn²⁺-doped $\text{Cs}_2\text{AgInCl}_6$ NCs. Photographs shown in the inset of panels h and i correspond to respective PL with 300 nm and Xe lamp excitation. Panels a–c are adapted from ref 183. Copyright 2018 American Chemical Society. Panel d is adapted from ref 564. Copyright 2019 American Chemical Society. Panel e is adapted with permission from ref 563. Copyright 2019 AIP Publishing. Panels f and g are adapted with permission from ref 556. Copyright 2018 John Wiley and Sons. Panels h and i are adapted from ref 566. Copyright 2018 American Chemical Society. Further permissions related to the material excerpted should be directed to the ACS.

hand, it has to be noted that the Tl-based compounds are highly toxic.⁵⁵⁵

Cu-Based NCs. Cu belongs to the group 11, and it is mostly existing in +2 or +1 oxidation states, and this can be a potential alternative for Pb. In general, Cu-based metal halides mostly crystallize in A_2CuX_4 or $\text{A}_3\text{Cu}_2\text{X}_5$ structures.^{45,556–559} As a remark, there are no Cu-X₆ octahedra in these structures. The interesting feature of these Cu-based NCs is that they exhibit relatively high PLQYs. For instance, Cs_2CuX_4 NCs can be easily prepared at room temperature by LARP, and the Cs_2CuCl_4 NCs that are obtained emit at 388 nm with 51.8% PLQY.⁵⁵⁶ In an another study, Booker *et al.*⁵⁵⁷ reported broadband green emission from Cs_2CuCl_4 NCs prepared by hot injection, and this is attributed to Cu-defect emission. The morphology of these NCs is tunable from dots to platelets and rods by varying the ratio of coordinating solvents. Moreover, the 0D $\text{Cs}_3\text{Cu}_2\text{I}_5$ NCs synthesized by hot injection exhibit intense emission at 445 nm with an absolute PLQY of ~87%, and this makes them promising for deep-blue LEDs.⁴⁵ These colloidal $\text{Cs}_3\text{Cu}_2\text{X}_5$ (X = I, Br/I, Br, Br/Cl, Cl) NCs can also be synthesized at room temperature through antisolvent precipitation and the prepared $\text{Cs}_3\text{Cu}_2\text{Cl}_5$ NCs emit green PL with near-unity PLQY.⁵⁵⁸ In this case, the origin of green PL is attributed to self-trapped exciton emission. However, further studies are needed to understand the origin of green emission and high PLQY. Nevertheless, the higher thermal

stability due to their inorganic nature, *eco-friendliness*, and high PLQY of these Cu-based NCs makes them promising for lighting and display applications.

Colloidal Double Perovskite NCs. Another promising lead-free perovskite system is the halide double perovskites (or elpasolites). These materials have the general formula $\text{A}_2\text{B(I)}\text{B}'(\text{III})\text{X}_6$ (see Figure 50). Charge neutrality is maintained by replacing two Pb(II) ions from $\text{A}_2\text{Pb}_2\text{X}_6$ (ABX_3) with one B(I) and one B'(III) ions, forming compounds like $\text{Cs}_2\text{AgBiCl}_6$ and $\text{Cs}_2\text{AgInCl}_6$. Colloidal syntheses of different double perovskite NCs have been reported.^{183,516,556,560–569} Figure 53a shows the UV-visible absorption and PL spectra of colloidal $\text{Cs}_2\text{AgBiCl}_6$ and $\text{Cs}_2\text{AgBiBr}_6$ NCs. The PL is significantly red-shifted from the band-edge absorptions and is believed to originate from defect and/or self-trapped excitons.^{570,571} Composition driven tuning of the band gap of double perovskite NCs has been attempted by many groups. For example, forming lower band gap materials like $\text{Cs}_2\text{AgBiI}_6$ is highly desirable for photovoltaics. Unfortunately, $\text{Cs}_2\text{AgBiI}_6$ in the bulk form could not be prepared owing to their positive heat of formation.⁵⁷² Interestingly, NCs of $\text{Cs}_2\text{AgBiI}_6$ can be prepared.^{183,573} Therefore, NC synthesis provides an addition handle to prepare compositions and phases of double perovskites, for which the corresponding bulk counterparts do not exist. Creutz *et al.* employed an anion exchange reaction converting

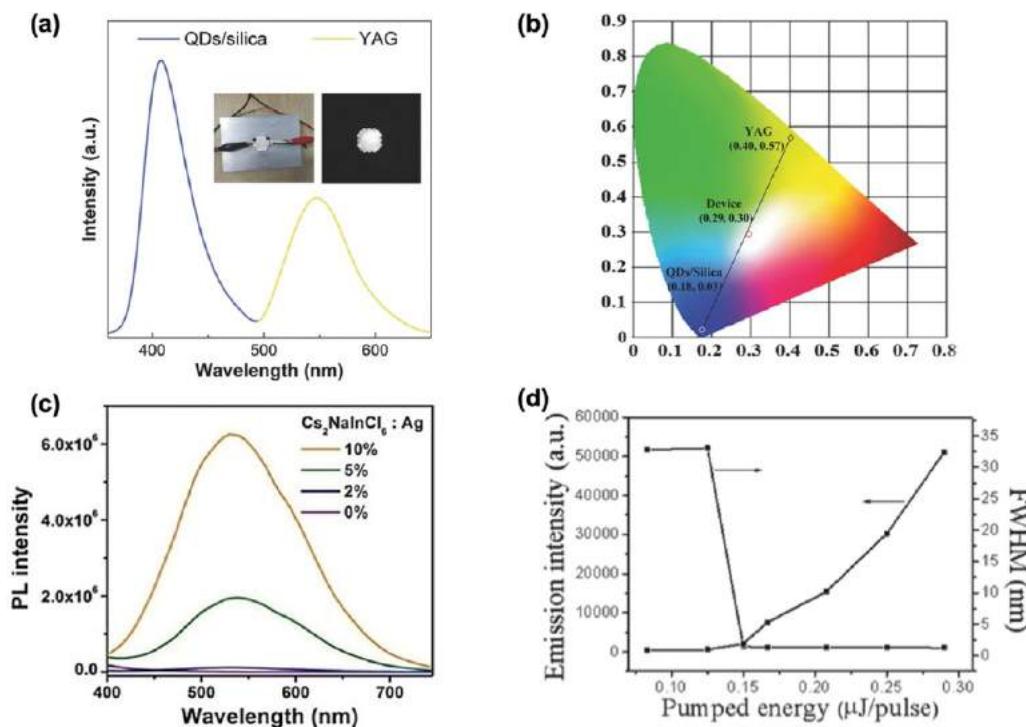


Figure 54. Applications of NCs of lead-free perovskite-inspired materials in light-emission applications. (a) Electroluminescence spectra and (b) CIE coordinates of the $\text{Cs}_3\text{Bi}_2\text{Br}_9$, blue phosphor and yellow YAG phosphor excited with a UV-emitting GaN LED, as well as the CIE coordinates of the overall white-light LED. (c) PL spectra of $\text{Cs}_2\text{NaInCl}_6$ alloyed with Ag. (d) Emission intensity and full-width at half maximum of CsSnI_3 quantum dots doped in a cholesteric liquid crystal as a function of the pump energy. Panels a and b are reprinted with permission from ref 551. Copyright 2017 John Wiley and Sons. Panel c is reprinted with permission from ref 576. Copyright 2019 John Wiley and Sons. Panel d is reprinted from ref 582. Copyright 2018 American Chemical Society.

$\text{Cs}_2\text{AgBiBr}_6$ NCs to $\text{Cs}_2\text{AgBiI}_6$ NCs (Figure 53b).¹⁸³ In general, the anion exchange reaction allowed them to control the X-site composition, and thereby tune the band gap and color of $\text{Cs}_2\text{AgBiX}_6$ NCs over a wide range, from 1.75 eV ($\text{Cs}_2\text{AgBiI}_6$) to 3.39 eV ($\text{Cs}_2\text{AgBiCl}_6$) (Figure 53c).¹⁸³ However, long-term stability of red-colored $\text{Cs}_2\text{AgBiI}_6$ NCs needs to be improved. In another report, Lamba *et al.* controlled the composition of B(I)-site of $\text{Cs}_2(\text{Na}_x\text{Ag}_{1-x})\text{BiCl}_6$ NCs to tune the optical band gap in the UV region (Figure 53d).⁵⁶⁴ Likewise, the composition at the B'(III)-site also can be controlled by forming $\text{Cs}_2\text{AgSb}_{1-x}\text{Bi}_x\text{Cl}_6$ NCs (Figure 53e).⁵⁶³

Typical double perovskite NCs have a cube shape (Figure 53e), which is similar to that of typical CsPbX_3 NCs. Most likely, appropriate surface chemistry will be required to prepare double perovskite NCs of different shapes. Fine tuning of reaction conditions is often required to avoid the formation of impurity phases like CsX , AgX , and $\text{Cs}_3\text{Bi}_2\text{X}_9$.¹⁹⁶ Furthermore, NCs of double perovskites containing Ag(I), *e.g.*, $\text{Cs}_2\text{AgSbCl}_6$ and $\text{Cs}_2\text{AgInCl}_6$, have a tendency to form small Ag NCs.⁵⁶⁰

Double perovskite NCs of $\text{Cs}_2\text{AgBiX}_6$ (X = Cl, Br) and $\text{Cs}_2\text{AgInCl}_6$ are reasonably stable for potential applications. Unfortunately, these NCs have wide band gaps, hence they absorb only high-energy (>2.5 eV) photons, and are therefore not suitable for single junction solar cells. Zhou *et al.* used $\text{Cs}_2\text{AgBiBr}_6$ NCs for the photocatalytic CO_2 reduction (see Figure 53fg), demonstrating photochemical conversion of CO_2 to solar fuels CO and CH_4 . In perspective, different double perovskite NCs should be tested for such photocatalytic applications. Another potential application of double perovskite NCs could be solid-state lighting. Luo *et al.* reported

warm white-light emission with ~86% PLQY from a bulk sample of Bi-doped $\text{Cs}_2(\text{Ag}_{0.6}\text{Na}_{0.4})\text{InCl}_6$,⁴⁹⁹ a result that was recently confirmed by Luo *et al.*, who reported warm white-light emission from Bi-doped $\text{Cs}_2(\text{Ag}_{0.6}\text{Na}_{0.4})\text{InCl}_6$ powders featuring a PLQY of 87.2%.⁴⁹⁹ The devices had a high stability and high-color rendering index.

Different reports on colloidal $\text{Cs}_2\text{AgInCl}_6$ and Bi-doped $\text{Cs}_2\text{AgInCl}_6$ NCs show similar broad emission with white or yellow color.^{560,566,574} For example, Figure 53h shows white-light emission with a broad emission spectrum significantly red-shifted from the absorption and PLE data.⁵⁶⁶ Therefore, the PL from such double perovskite NCs will not suffer from the vexing problems of self-absorption and Förster resonance energy transfer.⁵⁷⁵ The broad emission has been assigned to self-trapped exciton,^{499,576} but how it depends on different compositions is not yet well-understood. Yang *et al.*⁵⁷⁷ showed that the indirect band gap can be tuned to a direct band gap in $\text{Cs}_2\text{AgIn}_{x}\text{Bi}_{1-x}\text{Cl}_6$ double perovskite NCs by increasing the In content. The direct band gap double perovskite NCs exhibit higher absorption cross section and the PLQY as compared to indirect band gap ($\text{Cs}_2\text{AgBiCl}_6$) NCs.

Another approach to impart visible and near-infrared light emission is to dope luminescent metal ions like Mn^{2+} and lanthanides like Yb^{3+} and Er^{3+} .^{578,579} Figure 53i shows the red-colored light emission from Mn^{2+} -doped $\text{Cs}_2\text{AgInCl}_6$ NCs. Larger lanthanide ions require coordination number ≥ 6 to incorporate into the lattice. Typical semiconductors like Si, GaAs, and CdSe have coordination number = 4 for the metal ion, and are therefore not suitable for doping lanthanides. Interestingly, both ABX_3 perovskites and AB(I)B'(III)X_6 double perovskites with B-site coordination number = 6, can

incorporate lanthanide ions.⁵⁸⁰ Yb³⁺- and Er³⁺-doped Cs₂AgInCl₆ NCs with near-infrared emission at ~990 nm due to quantum cutting and 1540 nm (low-loss optical communication range) have been reported.^{565,568} Yb has also been reported to directly substitute Pb to form CsYbI₃ NCs with an emission wavelength 671 nm and could be synthesized by hot injection.⁵³⁹

Light-Emission Applications of Lead-Free Perovskite Nanocrystals. For light-emission, lead-free perovskite-inspired materials have mostly been used in applications involving optical excitation rather than charge injection. Namely, these applications are phosphors for white-light emitters and gain media for optically pumped lasers. For phosphors, one approach has been to use a UV GaN LED to excite blue-emitting quantum dots and a yellow-emitting phosphor to achieve white-light LEDs. Leng *et al.*⁵⁵¹ used Cs₃Bi₂Br₉ colloidal quantum dots as the blue-emitter (410 nm PL wavelength), and Y₃Al₅O₂ (YAG) as the yellow-emitter (broad PL centered at 551 nm wavelength). The white-light LED had CIE coordinates of (0.29,0.30) and a color temperature of 8477 K (Figure 54a,b).⁵⁵¹ Cs₃Bi₂Br₉ was advantageous because it forms a passivating BiOBr layer in the presence of moisture. This increases the PLQY, but also improves the stability of the quantum dots in the presence of moisture and acid. As a result, the Cs₃Bi₂Br₉ quantum dots could be mixed with TEOS, which was hydrolyzed with water and HBr to form silica. The resulting composite of quantum dots embedded in silica had improved stability, with the 72% of the PL being retained after 16 of exposure to a UV lamp, and 75% of the PL being retained after 16 h heat stressing at 60 °C.⁵⁵¹ Tan *et al.*⁵⁸¹ also demonstrated white-light LEDs using Cs₂SnCl₆ perovskites as the blue-emitter and Ba₂Sr₂SiO₄:Eu²⁺ and GaAlSiN₃:Eu²⁺ as the yellow phosphors. Under excitation from a UV GaN LED, the white-light LED had CIE coordinates of (0.36,0.37) and color temperature of 4486 K. The Cs₂SnCl₆:Bi exhibited blue emission at 455 nm, with a PLQY of 78.9%, which was higher than Cs₃Bi₂Br₉ (10-19% PLQY).^{551,581} The vacancy-ordered perovskite was also stable against moisture, due to the formation of a protective BiOCl layer and due to the tin cation already being in the more stable +4 oxidation state.⁵⁸¹ Yang *et al.* obtained lead-free blue-emitters with similarly high PLQYs of 32.8% using Eu²⁺-doped CsBr NCs. By combining these NCs with YAG:Ce³⁺ with a UV-emitting GaN LED, white emission with CIE coordinates of (0.32, 0.34) and color temperature of ~6300 K was obtained.⁵⁷⁰

Recently, it was demonstrated that white-light emission can be achieved using a phosphor comprising solely a double perovskite. Luo *et al.* demonstrated that powders of Cs₂(Ag_{0.6}Na_{0.4})InCl₆ doped with 0.04% Bi luminesces broadly across 400–800 nm wavelength (centered at 570 nm) with 86 ± 5% PLQY, and 1000 h stability.⁴⁹⁹ The broad emission arises due to the formation of a self-trapped exciton as a result of strong electron–phonon coupling and Jahn-Teller distortion in the AgCl₆ octahedron. By pressing Cs₂(Ag_{0.6}Na_{0.4})InCl₆ powder onto a GaN LED and encapsulating with silica, white-light emission was obtained through the blue emission from the LED mixing with the broad emission from the double perovskite phosphor. The white-light LED had CIE coordinates of (0.396, 0.448) and a color temperature of 4054 K, and stability over 1000 h in air.⁴⁹⁹ Han and co-workers also produced a series of works showing broad-band emission from Cs₂AgIn_xBi_{1-x}Cl₆, Ag-doped Cs₂NaInCl₆ and Mn²⁺-doped Cs₂NaIn_{0.75}Bi_{0.25}Cl₆ NCs.^{561,576,577} Cs₂AgBiCl₆ has an

indirect band gap, with low PLQY. Alloying In into this system resulted in a direct but parity-forbidden band gap. With increasing In content, the PLQY was found to increase up to 36.6% (with 90% In), along with an increase in broad emission centered at 570 nm wavelength. This was attributed to the emission from the parity-forbidden band gap, which prevents absorption but allows radiative recombination.⁵⁸³ Cs₂NaInCl₆ has a wide band gap of 4.55 eV but almost no PL. Alloying with Ag resulted in an increased PLQY from a broad-band sub-band-gap emission, reaching up to 31.1% with 10% Ag. These results were attributed to a dark self-trapped exciton being present in Cs₂NaInCl₆ that became bright with Ag alloying by breaking the parity-forbidden transition in Cs₂NaInCl₆ (Figure 54c).⁵⁷⁶ The self-trapped exciton in Cs₂NaIn_xBi_{1-x}Cl₆ is also believed to be dark, with only blue PL due to free excitons. Broad-band yellow emission was obtained by doping with Mn²⁺, which resulted in a PLQY of 44.6% being obtained. This broad-band transition was attributed to the dark self-trapped exciton transferring to the ⁴T₁ excited state of Mn²⁺ and relaxing to give PL.⁵⁴⁶ Recently, Lee *et al.* have reported characteristic absorption features in the Na/Bi³⁺ system. Cs₂NaBiCl₆ NCs and Cs₂NaBiBr₆ NCs showed sharp and discrete single peaks assigned to the s–p transition (6s² → 6s¹p¹) from the [BiX₆]³⁻ units within the crystal lattice of elpasolite structures. Such discrete optical transition characteristics have not been observed for Ag/M³⁺ DP or for Cs₃Bi₂X₉ materials.^{569,584} A series of studies on Bi-doped Cs₂Na_{1-x}Ag_xInCl₆ and Cs₂Na_{1-x}Ag_xBiCl₆ NCs were recently reported in which the extent of Ag/Na alloying was found to regulate the PLQY of the NCs.^{506,567} Light emission in these materials was identified to arise from recombination from carriers trapped in localized states. A combined experimental and computation study showed that the extent of localization of the holes (which were found to be localized at AgCl₆ octahedra), was strongly dependent on the amount of Na⁺ ions, that is, on the average number of NaCl₆ octahedra surrounding each individual AgCl₆ octahedron. In essence, the higher this number, the more likely is for the holes to stay localized, and the higher is the PLQY. Also, the same authors found that, regardless of the type of ligands used in the synthesis and of any post-synthesis ligand exchange that was attempted, the PLQY for these materials could not be increased beyond 37%, against the 86% reported for the bulk.⁵⁰⁸ Their conclusion, based also on a series of experiments and calculations, was that unpassivated surface traps are most likely responsible for the lower PLQY, and therefore, these materials are much less surface tolerant than the corresponding Pb-based halide perovskites.

Beyond the use of lead-free perovskite-inspired materials for phosphors, tin- and germanium-based perovskites have been demonstrated as potential gain materials for optically pumped lasing. Xing *et al.* demonstrated amplified spontaneous emission (ASE) across the visible to near-infrared (700–950 nm wavelength) from CsSnBr_xI_{3-x} thin films.⁵²⁵ By reducing the trap density in the thin films through the addition of SnF₂ during synthesis, the lasing threshold in CsSnI₃ was reduced to a low value of 6 μJ cm⁻² (whereas lasing was not obtained in the films without SnF₂) and a quality factor exceeding 500. Lee *et al.*⁵⁸² synthesized CsSnI₃ quantum dots 3–5 nm in size, which were doped into a cholesteric liquid crystal (CLC). The CsSnI₃ quantum dots acted as the gain medium, and the CLC as the optical resonator. The lasing threshold was ~0.8 mJ cm⁻² pulse⁻¹, but the quality factor was ~2000. The device was

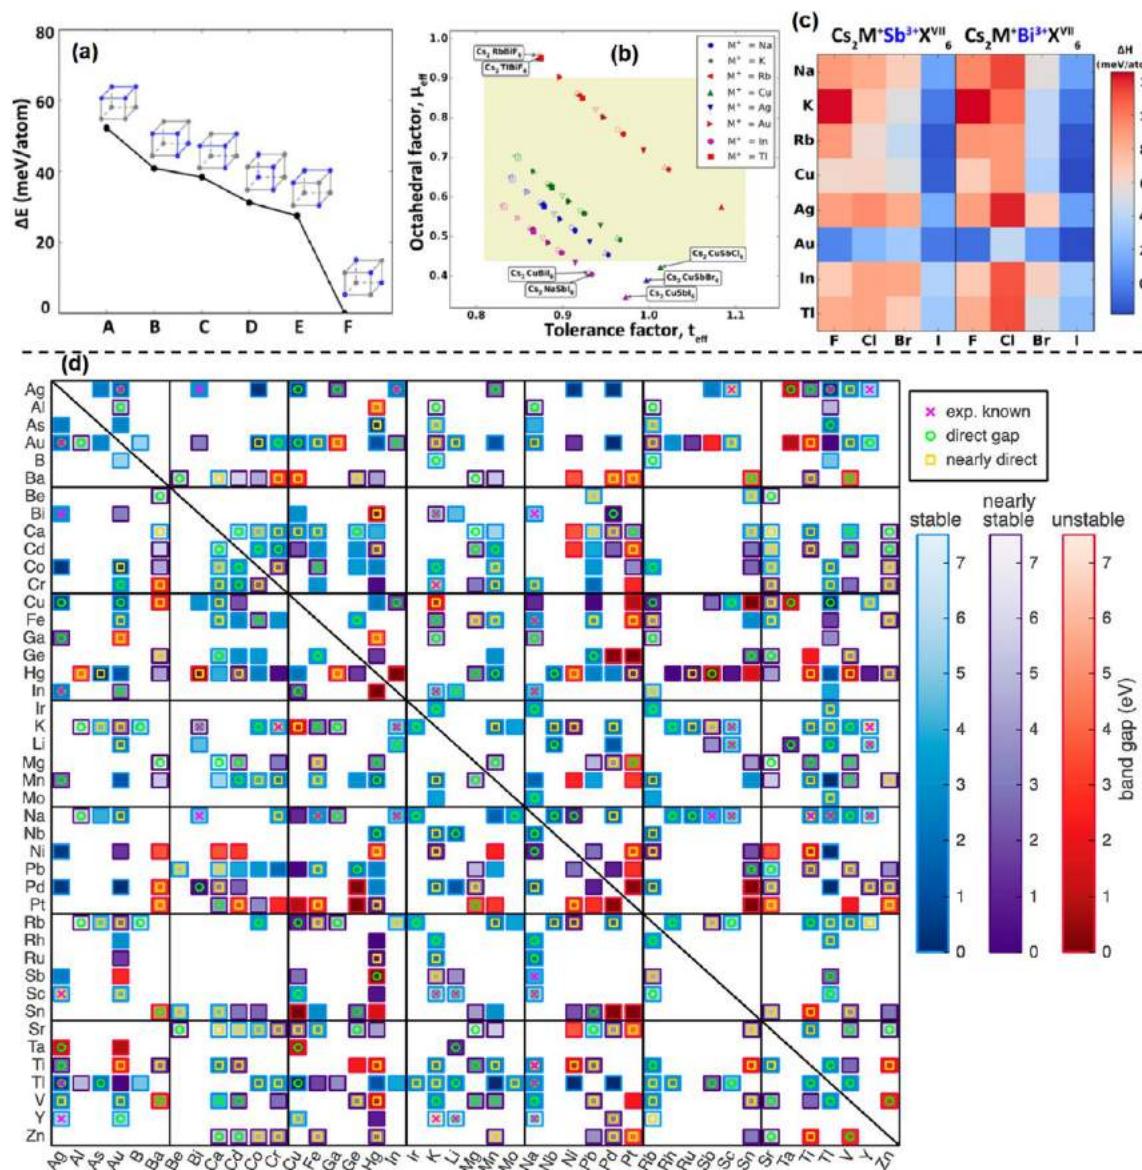


Figure 55. (a) Total energies for different arrangements $[\text{AgX}_6]^{5-}$ and $[\text{BiX}_6]^{3-}$ octahedral motifs calculated in a $2 \times 2 \times 2$ supercell of $\text{Cs}_2\text{AgBiCl}_6$. The energy for most stable configuration (F) is set at zero. (b) Evaluation of structural stability of different $\text{Cs}_2\text{B}(\text{I})\text{BiX}_6$ and $\text{Cs}_2\text{B}(\text{I})\text{SbX}_6$ with varying compositions for B(I) (indicated by M^+ in the figure) and X, on the basis effective tolerance factor (t_{eff}) and octahedral factor (μ_{eff}) variables. The compositions present outside the inner square are unstable. Red, green, blue, and maroon colors correspond to F, Cl, Br, and I, respectively. The open and filled symbols specify Sb- and Bi-containing perovskites, respectively. (c) Thermodynamic stability of the double perovskite compositions calculated using decomposition enthalpy (ΔH). Higher positive values of ΔH indicate more stable compositions. (d) Map showing calculated thermodynamic stability, band gap, and experimental existence for a large number $\text{Cs}_2\text{BB}'\text{Cl}_6$ double perovskite compositions with different combinations of B and B', shown along the axes. The map is mirrored across the diagonal line because B and B' are treated equivalently. Details of calculation and classification such as stable, nearly stable, and unstable are given in ref 589. Panels a–c are adapted from ref 590. Copyright 2017 American Chemical Society. Panel d is adapted from ref 589. Copyright 2020 American Chemical Society.

also air-stable, with the lasing emission intensity decreasing only by 13% after 6 months of storage in air compared to the initial intensity.⁵⁸² Hints of amplified spontaneous emission was also found in $\text{CH}_3\text{NH}_3\text{Sn}_{0.5}\text{Ge}_{0.5}\text{I}_3$ by Nagane *et al.*,⁵⁸³ in which the PL fwhm decreased from 75 to 40 nm when the excitation density was increased from 10^{15} to 10^{16} cm^{-3} . This 50% mixture of Sn and Ge was also found to give the lowest Urbach energy (of 47 meV) across the Sn–Ge composition series.⁵⁸³ Recently, Moon *et al.*⁵⁸⁹ reported the synthesis of high-quality cesium ytterbium triiodide (CsYbI_3) cubic perovskite NCs with a PLQY of 58%. It was found that the

CsYbI_3 NCs exhibit a high photoresponsivity ($2.4 \times 10^3 \text{ A W}^{-1}$) with an EQE of $5.8 \times 10^5\%$.

Designing Additional Double Perovskite Compositions. The exploration of Pb-free materials is driven by theoretical predictions.^{586–588} Based on the above discussion, it appears that, (i) the optoelectronic properties of Pb-free perovskites are still inferior compared to Pb-halide perovskites, and (ii) only a few double perovskite compositions have been explored so far, while there are hundreds of possible compositions for metal-halide double perovskite that have yet to be explored.⁵⁸⁹ The most important criteria when

screening materials based on computations are (i) thermodynamic stability, (ii) band gap (which should be <2.5 eV), and (iii) effective masses of charge carriers (which should be <1 electron mass). Additional screening criteria include trap energy, along with the low toxicity and earth abundance of the elements.

The stability of double perovskites strongly depends on the structural parameters. $A_2B(I)B'(III)X_6$ has two kinds of octahedral motifs like $[B(I)X_6]^{5-}$ and $[B(III)X_6]^{3-}$. For example, in $Cs_2AgBiCl_6$, the motifs are $[AgX_6]^{5-}$ and $[BiX_6]^{3-}$ and are represented by blue and gray dots, respectively, in Figure 55a. In a crystal, the octahedral motifs can be arranged in six different ways (A–F), as shown in Figure 55a. For $Cs_2AgBiCl_6$, it is found that the F arrangement, *i.e.*, with $[AgX_6]^{5-}$ and $[BiX_6]^{3-}$ motifs being arranged alternatively, gives the thermodynamic stable state. This thermodynamic stability of F arrangement is at the basis of double perovskite structure shown in Figure 50.

For ABX_3 perovskites, the structural stability can be described by the Goldschmidt tolerance factor [$t = (r_A + r_X)/\sqrt{2(r_B + r_X)}$] and octahedral factor ($m = r_B/r_X$). These are defined using the idealized solid-sphere model, where r_A , r_B , and r_X are the ionic radii of A, B, and X, respectively. It has been found empirically that for the formation of ABX_3 halide perovskites requires $0.81 < t < 1.11$ and $0.44 < \mu < 0.90$.⁵⁹¹ For $A_2B(I)B'(III)X_6$ double perovskite, there are two B-site cations, and therefore, $t_{eff} = (r_A + r_X)/\sqrt{2\{(r_B + r_{B'})/2 + r_X\}}$ and $m_{eff} = (r_B + r_{B'})/2r_X$. The shaded region in Figure 55b empirically suggests the requirement of t_{eff} and m_{eff} to form stable double perovskite of $Cs_2B(I)BiX_6$ and $Cs_2B(I)SbX_6$ with varying compositions for B(I) (indicated by M^+ in the figure) and X. Such crystallographic parameters provide the initial assessment regarding the formability of a double perovskite composition. Furthermore, one can calculate the decomposition enthalpy (ΔH) for double perovskites using DFT (Figure 55c). In the present calculation,⁵⁹⁰ positive values of ΔH indicate thermodynamic stability. Particularly, samples with $\Delta H > 20$ meV/atom are expected to be stable. Figure 55c shows that the iodide compositions show poor thermodynamic stability, which also corroborates the fact that many iodide compositions have μ values that are too small and inhibit the formation of octahedral motifs. This instability of iodide double perovskites has also been observed experimentally is most likely the main reason for the absence of experimentally observed narrow (~ 2 eV) band gap double perovskites. Fluoride-based double perovskites are also stable, but often not the preferred material for optoelectronics, since the high electronegativity of fluoride is expected to yield wide band gap insulating materials.

High stability and the possibility of reasonably narrow band gap led Bartel *et al.* to screen 311 compositions of $Cs_2B(I)B'(III)Cl_6$.⁵⁸⁹ The mapping of these compounds, showing their thermodynamic stability, nature of the band gap, and whether they exist experimentally is displayed in Figure 55d. They could identify about 47 nontoxic double perovskite compositions with direct or nearly direct (within 100 meV) computed band gaps between 1 and 3 eV. However, many of these compositions need experimental verification.

Summary and Future Outlook for Pb-Free MHP NCs.

Various colloidal Pb-free metal-halide perovskite NCs like $Cs_3B_2X_9$ (B = Sb and Bi), $CsBX_3$ (B = Sn and Ge), and

Cs_4SnX_6 have prepared in recent years. $CsSnX_3$ and $CsGeX_3$ NCs are unstable. By contrast $Cs_3Sb_2X_9$, $Cs_3Bi_2X_9$ and Cs_4SnX_6 NCs have improved stability, but charge transport is restricted due to reduced structural dimensionality (2D or 0D) in these materials. Nevertheless, these materials may find applications as stable blue phosphors, which can be used in combination with yellow phosphors for white-light emission. Interestingly, non-perovskite TlX possesses similar electronic structure to $CsPbX_3$ and have demonstrated promising optoelectronic properties in the UV-blue region. However, Tl compounds are highly toxic.

Despite reasonable progress in the synthesis of double perovskite NCs, a better understanding of the origin of PL is required to tune the intensity, peak energy and shape of the broad PL, by fine tuning the composition. Compositional fine tuning is also expected to suppress the effect of reduction of $Ag(I)$ to $Ag(0)$ on the PL. Furthermore, doping with lanthanides (Yb^{3+} , Er^{3+} , *etc.*) can provide intense near-infrared emission, required for optical communication, infrared LEDs and remote sensing. Exploring light emission properties of metal-halide double perovskites and their derivatives for real life application is an important future direction. However, an important limitation of the double perovskites is their wide and/or indirect band gap. Therefore, different classes of double perovskite compositions need to be synthesized both in the bulk and nanocrystalline form. Recent work also suggests that the band gap could be reduced in alloys between compounds that form a type II alignment.²³⁷ We hope that, in near feature, researchers will develop stable metal-halide double perovskite compositions with <2 eV band gap, along with good charge transport properties. In the search for different Pb-free perovskite semiconductors, compositions of chalcogenide perovskites,⁵⁹² mixed-halide chalcogenide perovskites⁵⁹³ and oxide perovskites⁵⁹⁴ provide additional options.⁵⁹⁵

Finally, very little is reported on the use of perovskite derivative NCs in electrically driven applications, such as LEDs, although recent work on thin films motivates this effort. Of the handful of examples of lead-free NC LEDs, recent reports of $Cs_3Cu_2I_5$ are some of the more promising. 1.12% EQE was achieved, with deep blue emission.⁵⁹⁶ The devices exhibited reasonable stability with a half-life of more than 100 h.⁵⁹⁶ In addition, Ma *et al.*⁵⁴⁷ demonstrated LEDs from $Cs_3Sb_2Br_9$ quantum dots, with electroluminescence at 408 nm (violet color) and an EQE of 0.2%. $Cs_3Sb_2Br_9$ is a particularly suitable material for demonstration in LEDs given that they have a PLQY of 51.2%, which is larger than other $A_3B_2X_9$ quantum dots. $Cs_3Sb_2Br_9$ is also stable against heat, UV illumination, air and the presence of moisture, and the LEDs retained 90% of the initial electroluminescence intensity after 6 h of operation at 7 V (~ 70 mA cm $^{-2}$ current density).⁵⁴⁷ This is an improvement over many Pb-based perovskite quantum dots. In thin films, Rand *et al.* found that near-infrared LEDs with Pb–Sn perovskites had a 2 orders of magnitude improvement in radiance when the films were grown with the addition of a bulky organoammonium halide ligand to passivate the surface and reduce the grain size to better confine carriers.⁵⁹⁷ NCs with carefully chosen ligands could therefore be worth investigation. Furthermore, Zhang *et al.*⁵⁹⁸ recently demonstrated electroluminescence from self-trapped excitons in thin films of a Ruddlesden-Popper ($C_{18}H_{35}NH_3)_2SnBr_4$ perovskite. This perovskite was synthesized by hot injection to form microplates, and self-trapping occurred in the $[SnBr_6]^{4-}$, which are electronically isolated from neighboring

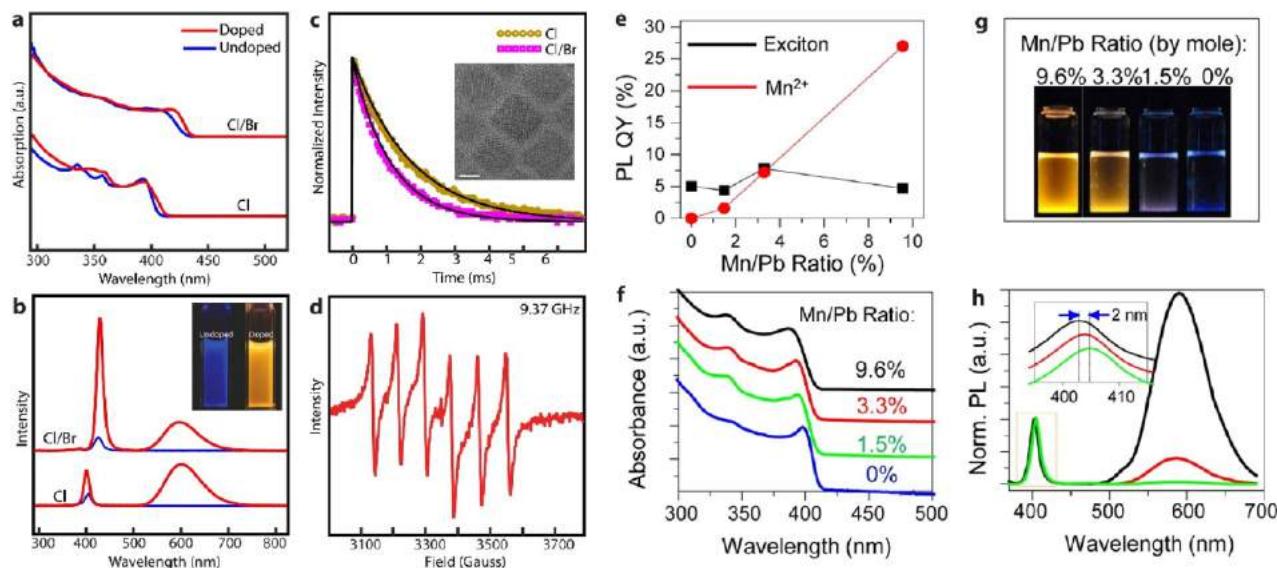


Figure 56. Synthesis and properties of Mn^{2+} -doped $CsPbCl_3$ NCs. (a) Absorption and (b) PL spectra of Mn^{2+} -doped $CsPbCl_3$ and $CsPbCl_xBr_{3-x}$ NCs with those of undoped control samples. (c) Time-dependent PL decay of Mn phosphorescence. (d) EPR signal from Mn^{2+} -doped $CsPbCl_3$ NCs. Images in a–d were taken from ref 604. Copyright 2016 American Chemical Society. (e) Dependence of exciton and Mn^{2+} PLQY on dopant concentration. (f,h) Normalized absorption and (f) PL spectra (h) of Mn^{2+} -doped $CsPbCl_3$ NCs of varying dopant concentration. Increased Mn^{2+} content is associated with a gradual blue shift of both the band-edge peak in absorption and the intrinsic NC PL peak (expanded in the inset of panel d); this can be attributed to the effects of alloying on the NC band structure. The intensity of Mn^{2+} emission increases with increasing the Mn^{2+} content with out effecting the peak position. (g) Photograph of hexane solutions of Mn^{2+} -doped $CsPbCl_3$ NCs of varying Mn^{2+} content illuminated by a UV lamp (365 nm). Solutions were diluted to exhibit the same optical density at 365 nm. Images in e–h were taken from ref 605. Copyright 2016 American Chemical Society.

Sn–Br layers by the long oleylamine cations. Electroluminescence from the self-trapped exciton (centered at 625 nm wavelength) was obtained, with 350 cd m^{-2} and 0.1% EQE achieved. The turn-on voltage was low, at 2.2 V, and it was believed that electrons and holes were directly injected into the self-trapped states.^{597,598} This motivates future efforts to (i) understand the nature and behavior of the self-trapped exciton in the quantum-confined regime (*i.e.*, in very small size NCs); (ii) explore how to narrow the PL line width (*i.e.*, by varying the composition); (iii) improve charge injection into the NCs; and (iv) to further investigate other optical properties, such as anti-Stokes shifted PL.^{599,600} Finally, the ambitious goal would be to achieve white-light electroluminescence from self-trapped excitons in double perovskites.

DOPING (A AND B-SITES) OF MHP NCs

B-Site Doping. Doping in metal-halide perovskite NCs has been extensively studied to improve their optical and electronic properties and structural stability by modifying the electronic structure or introducing additional channels of energy and charge transfer. Both A- and B-site doping with various mono-, di- and trivalent metal ions have been explored for this purpose. In general, A- and B-site doping can be achieved either by cation exchange or through *in situ* synthesis.^{108,573,601,602} Doping through cation exchange is briefly introduced in the section named **Composition Control by Ion Exchange and Suppression of Exchange**. In this section, we provide an extensive discussion on the recent progress made on A- and B-site-doped MHP NCs for improved stability and enhanced PLQY and the characterization of the additional properties resulting from doping in metal-halide perovskite NCs. In particular, special attention is paid to the Mn^{2+} - and lanthanide-doped perovskite NCs, which have been widely

studied over the years due to their interesting properties and potential applications.

Mn^{2+} Doping in Perovskite Nanocrystals. Mn^{2+} -doped colloidal semiconductor NCs have been a topic of intensive research for many decades, because the doping can introduce various additional optical, electronic, and magnetic properties through the interaction of the exciton with dopants.^{602,603} In Mn^{2+} -doped semiconductors, the exciton energy transfer from a semiconductor host to Mn^{2+} dopants leads to orange emission by a spin-forbidden $^4T_1 \rightarrow ^6A_1$ Mn d–d transition. With the emergence of halide perovskites as a novel class of semiconductors, the Mn^{2+} doping concept has been extended to this class of materials and significant progress has been made over the last few years. Currently, doping of Mn^{2+} in halide perovskite NCs has been demonstrated mostly in cesium lead-halide NCs ($CsPbX_3$, X = Cl, Br, I).

Mn^{2+} Doping in $CsPbCl_3$ NCs. The initial successful Mn^{2+} doping of metal-halide perovskite NCs was performed in $CsPbCl_3$ NCs with nanocube morphology, which was reported by two different groups in 2016 (Son group and Klimov group).^{604,605} Mn^{2+} doping in $CsPbCl_3$ NCs was achieved by adding $MnCl_2$, an additional reactant as the source of Mn^{2+} , under the typical hot-injection synthesis conditions of $CsPbCl_3$ NCs. This resulted in doping of Mn^{2+} at the level of <1 to 10%, which showed distinct Mn^{2+} luminescence centered around 600 nm resulting from the sensitization of the Mn^{2+} ligand field transition. In this synthesis, $MnCl_2$ was the most effective precursor of Mn^{2+} ions, though many other precursors such as $Mn(ac)_2$, $Mn(acac)_2$, and $Mn(oleate)_2$ were also used as dopant precursors. However, in contrast to $MnCl_2$ and $CsPbCl_3$ pair for Mn^{2+} doping, extending the same approach to doping of Mn^{2+} in $CsPbBr_3$ NCs using $MnBr_2$ was not successful. On the other hand, when $MnCl_2$ was used as precursor for Mn^{2+} doping in $CsPbBr_3$,⁶⁰⁶ Mn^{2+} -doped Cl/Br

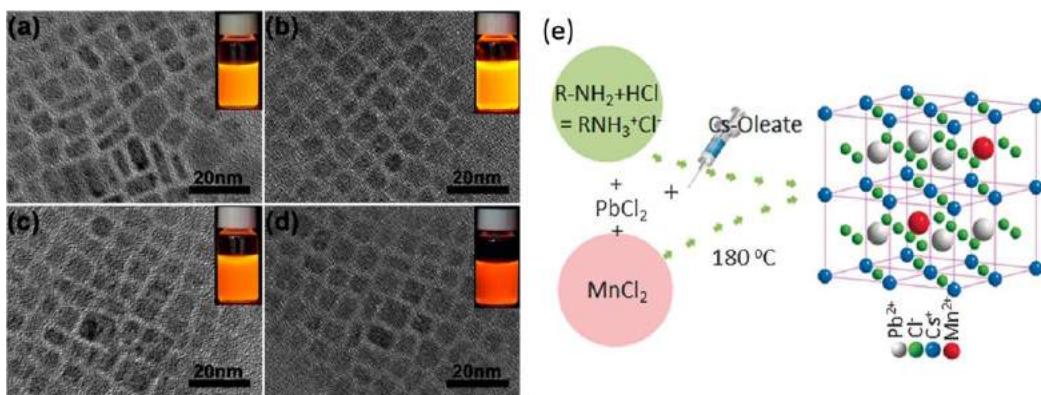


Figure 57. Heavy Mn²⁺ doping in CsPbCl₃ NCs. (a–d) TEM images of the CsPb_xMn_{1-x}Cl₃ NCs that are prepared with Pb to Mn molar feed ratios of 1:1.25 (a), 1:2.5 (b), 1:5 (c), and 1:10 (d) at 170 °C; $x = 0.02, 0.04, 0.10$, and 0.27, respectively. Insets: Corresponding PL images excited by 365 nm UV light. Panels a–d are reprinted from ref 606. Copyright 2017 American Chemical Society (e,f) Two additional methods of increasing Mn²⁺ doping level in CsPbCl₃ NCs. Panel e is reprinted with permission from ref 608. Copyright 2017 John Wiley & Sons, Inc.

mixed-halide NCs were obtained. This suggests that the formation of the Mn–Cl bond is preferred over that of the Mn–Br bond when attempting doping using Mn²⁺ halide as the precursor. Figure 56a,b shows the absorption and photoluminescence spectra of the undoped and Mn-doped CsPbCl₃ and CsPb(Cl/Br)₃ NCs synthesized using MnCl₂ as the Mn²⁺ precursor at a doping concentration of <1%. The characteristic Mn²⁺ photoluminescence appearing at ~600 nm indicates the doping of Mn²⁺ ions into perovskite NC hosts. The resultant Mn²⁺ photoluminescence is caused by the energy transfer from the host to d-d transition of Mn²⁺ ions. At low doping concentrations, the Mn²⁺ luminescence exhibits nearly single exponential decay, as expected from the relatively homogenous ligand field environment and weak interdopant coupling. EPR data of Mn-doped CsPbCl₃ with <1% doping also showed the characteristic fine structure of Mn²⁺ expected from cubic lattice symmetry, confirming the successful doping of Mn²⁺ in the NC host.

In later studies on Mn²⁺ doping in CsPbCl₃ NCs, additional efforts were made to increase the doping concentration. In principle, heavily doped NCs should be called alloys rather than doped NCs, because doping in NCs generally refers only to a few dopants per NCs.⁶⁰⁷ However, most often heavily doped NCs are still called doped NCs.⁶⁰⁶ Herein, we do not make any difference between alloys and doped NCs for readers to avoid confusion with the current literature. Exploration of these heavily doped or alloy NCs were partially motivated by the desire to replace Pb with less toxic elements, and this is important for practical applications of perovskite NCs. For example, Liu *et al.* reported the Mn²⁺ substitution ratio is up to 46% and a luminescence quantum yield of 56% in CsPbCl₃, which was achieved using the higher Mn/Pb ratio in the reactant mixture (Figure 57a–d).⁶⁰⁶ Das Adhikari *et al.* reported another method of increasing the Mn²⁺ doping concentration by using oleylammonium chloride as an additional reactant (Figure 57e).⁶⁰⁸ In addition to the hot-injection doping, room-temperature Mn²⁺ doping was also demonstrated. Xu *et al.* reported Mn²⁺ doping at room temperature using non-halide Mn²⁺ precursors.⁶⁰⁹ In their report, they used metal acetate salts as the precursor, which were converted to metal-oleate complexes in the presence of ligands, and then added HCl to protonate the carboxylate group, increasing the amount of monomer initiating the

formation of nanocubes. The presence of HCl also promoted a Cl-rich surface, supplying ample binding sites for Mn²⁺ ions and facilitating Mn²⁺ doping. Further coating of Mn²⁺-doped CsPbCl₃ with an additional CsPbCl₃ shell improved the Mn²⁺ luminescence quantum yield. Recently, Paul *et al.*⁶⁰² reported that the size distribution of CsPbCl₃ NCs significantly improves with slight doping of Mn²⁺ ions during their synthesis by an ultrasonication approach (Figure 58a,b). This results in a prominent excitonic resonance for Mn²⁺-doped CsPbCl₃ NCs as compared to pure CsPbCl₃ NCs. (the reader is directed to the OPTICAL PROPERTIES section for more

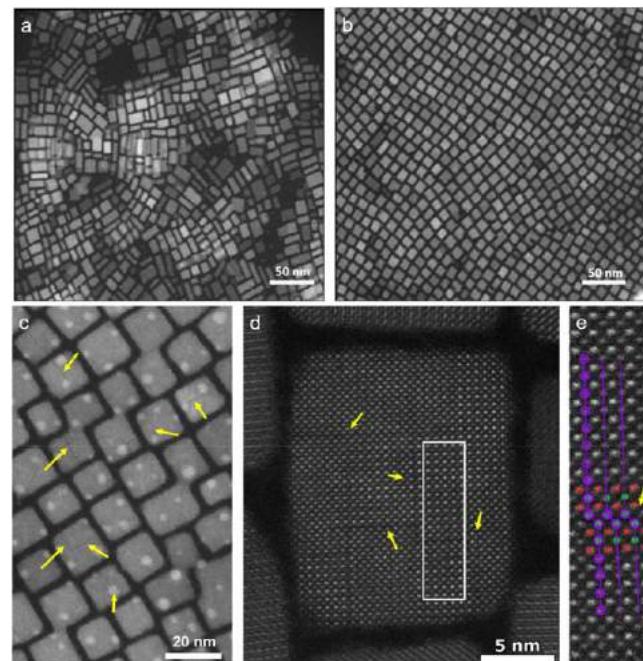


Figure 58. Overview TEM images of (a) pure and (b,c) Mn²⁺-doped CsPbCl₃ NCs (Mn to Pb feed ratio 3:1), as shown in (c), with a large number of NCs have one or more line defects. (f,g) Corresponding atomically resolved HAADF-STEM image showing R–P defect planes (Pb/Mn–Cl = red, Cs = green). The lattices are shifted half of the unit cell at the grain boundaries. Panel a–e are reprinted with permission under a Creative Commons CC-BY 4.0 license from ref 602. Copyright 2020 John Wiley & Sons, Inc.

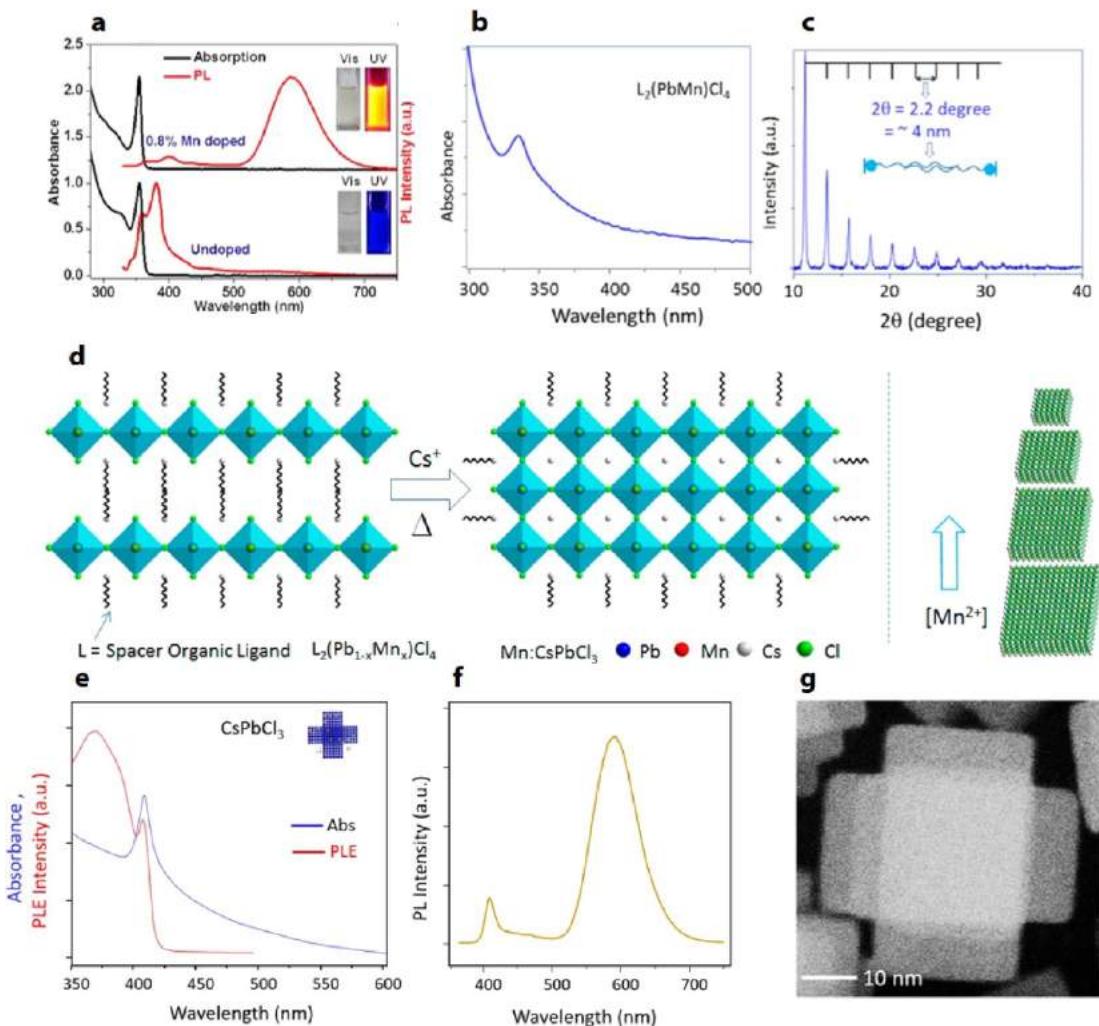


Figure 59. Mn²⁺ doping of anisotropic CsPbCl₃ NCs. (a) Absorption and PL spectra of undoped and 0.8% Mn²⁺-doped CsPbCl₃ nanoplatelets. Panel a is reprinted from ref 238. Copyright 2017 American Chemical Society. (b) Absorption spectra of the layered perovskites. The peak at 334 nm is characteristic of the monolayered structures. (c) Powder X-ray diffraction pattern of the layered perovskites. The interpeak spacing was 2.2° (2θ), which corresponds to ~4 nm. (d) Schematic presentation of formation of doped perovskites from layered perovskites L₂(Pb_{1-x}Mn_x)Cl₄. L stands for *n*-butylammonium and oleylammmonium ions. The schematic shows Mn²⁺ concentration in the reaction mixture to control the size of Mn²⁺-doped platelets. With the increase of the amount of Mn²⁺ in layered perovskites, the surface area of the platelets decreases. Panels b–d are reprinted with permission from ref 610. Copyright 2018 American Chemical Society. (e) Absorption and PLE spectra of Mn²⁺-doped CsPbCl₃ hexapod nanostructures. PLE was measured at Mn²⁺ PL maxima. (f) PL spectra of Mn²⁺-doped CsPbCl₃ armed structures. Excitation wavelength was 350 nm. (g) HRSTEM of Mn²⁺-doped CsPbCl₃ hexapod. Panels e–g are reprinted from ref 611. Copyright 2019 American Chemical Society.

details). Interestingly, it was observed that Mn²⁺ doping leads to the formation of R–P defects within the host NCs, in which (Pb/Mn)–Cl atomic columns were shifted by half a unit cell at the border of the defect planes (Figure 58c–e), thus inducing quantum confinement within the host NCs. This results in a gradual blue shift of excitonic absorption and PL peaks. The authors hypothesized that the formation of such R–P defects may be triggered by the size difference between Mn²⁺ (1.6 Å) and Pb²⁺ (2.38 Å) ions.

Although earlier studies focused on Mn²⁺ doping in cube-shaped CsPbCl₃ NCs with very weak quantum confinement, more recent studies reported the synthesis of CsPbCl₃ NCs of different morphologies, such as NPs with strong confinement and branched structures. Mir *et al.* synthesized Mn²⁺-doped CsPbCl₃ NPs of thickness 2.2 nm, which exhibit strong quantum confinement along the thickness direction (Figure 59a).²³⁸ Das Adhikari *et al.* reported another method of doping

Mn²⁺ in CsPbCl₃ NPs, which involves the initial synthesis of a Mn²⁺-doped monolayer structure and subsequent formation of NPs by the addition of cesium-oleate.⁶¹⁰ They synthesized 5-nm-thick NPs with different lateral sizes (20–580 nm) that varied with the amount of Cs⁺ and Mn²⁺ employed in the reaction (Figure 59b–d). Quantum confinement of the exciton in Mn²⁺-doped semiconductor NCs can enhance the exciton–dopant interaction, which determines various magneto-optical properties. Continued progress in the synthesis of strongly confined Mn²⁺-doped perovskite NCs is important for expanding their applicability. In another study, Mn²⁺-doped CsPbCl₃ branched hexapods were synthesized using a seeded growth approach.⁶¹¹ Cores were first formed under halide-deficient conditions. In the second step, the reaction was enriched with halides to facilitate the arm growths. In the presence of Mn²⁺ precursor in the second step, the final

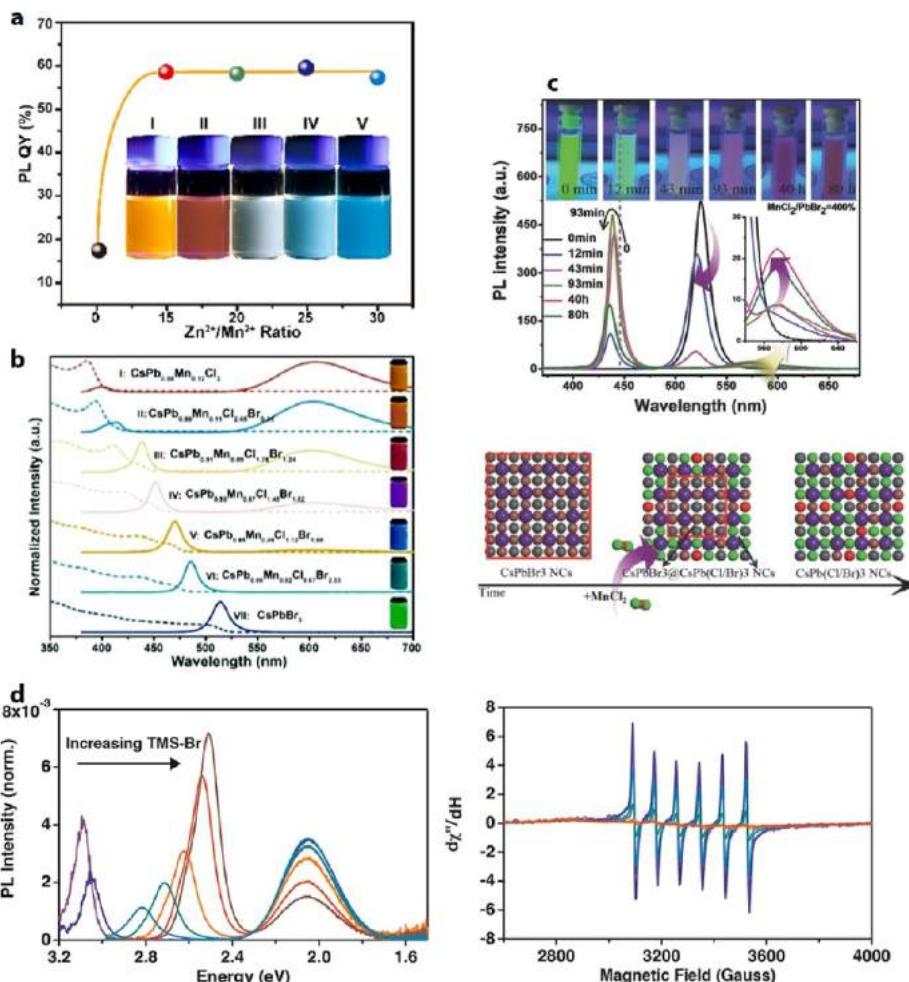


Figure 60. Post-synthesis anion exchange of Mn²⁺-doped CsPbCl₃. (a) PLQY vs Mn²⁺ content of the initial and ion exchanged CsPb_{0.75}Cl₃:0.25Mn²⁺ NCs. The initial NCs have a low QY of 17.8%. After ion exchange, the QY of the samples sharply increases to 59.3% and maintains that level with the increasing ion exchange reaction time. The photographs of the pristine CsPb_{0.75}Cl₃:0.25Mn²⁺ NCs and ion-exchanged NCs with different reaction times under 365 nm UV lamp illumination. The color changes come from the decrease of the Mn²⁺ content. Reprinted from ref 311. Copyright 2018 American Chemical Society. (b) UV-vis absorption (dashed line) and photoluminescence spectra (solid line) of Cs(Pb_xMn_{1-x})(Cl_yBr_{1-y})₃ NCs. Reprinted with permission from ref 612. Copyright 2017 Royal Society of Chemistry. (c) Temporal evolution of PL spectra of CsPbBr₃ NCs after adding the MnCl₂ precursor. The inset is the corresponding digital photograph at different times under the irradiation of a 365 nm UV lamp. Sketch of the ion exchange process from pure CsPbBr₃ NCs *via* adding MnCl₂ precursor. Images were taken with permission from ref 613. Copyright 2017 John Wiley and Sons. (d) PL spectra (left) and EPR spectra (right) of 1.1% Mn²⁺-doped CsPbCl₃ NCs in the EPR tube during the course of an anion exchange reaction; note that Mn²⁺ PL is seen centered at ~610 nm at every stage of the anion exchange reaction. The PL spectra are each normalized to their total integrated PL intensity. A 365 nm diode was used for excitation. Each spectrum was taken at the same NC concentration, and the NCs were never removed from the EPR tube over the entire experiment. Panels d and e are reprinted from ref 614. Copyright 2019 American Chemical Society.

product consisted of Mn²⁺-doped branched CsPbCl₃ NCs (Figure 59e–g).⁶¹¹

Mn²⁺ Doping in CsPbBr₃ NCs. Most of the work on Mn²⁺ doping of CsPbX₃ NCs has focused on CsPbCl₃ despite its less desirable optical properties than other halide systems (higher band gap and lower luminescence quantum yield). This is because doping of Mn²⁺ is most favorable in CsPbCl₃ host and becomes increasingly more difficult for bromide and iodide perovskite NCs. Simply extending the doping method used for producing Mn²⁺-doped CsPbCl₃ NCs described above did not produce Mn²⁺-doped CsPbBr₃ NCs. It was hypothesized in the work by Liu *et al.* that direct hot-injection synthesis of Mn²⁺-doped CsPbBr₃ using MnBr₂ was energetically unfavorable owing to the large difference in bond energy between Pb–Br (249 kJ/mol) and Mn–Br (314 kJ/mol) compared to that between Pb–Cl (301 kJ/mol) and Mn–Cl (338 kJ/mol).⁶⁰⁵

The authors argued that the higher stability of the Mn–Br bond compared to the Pb–Br bond prevented the incorporation of Mn²⁺ into the CsPbBr₃ lattice. Because of the difficulty of direct Mn²⁺ doping in CsPbBr₃ NCs, various post-synthesis doping methods were developed.

In an early attempt by Li *et al.*³¹¹ post-synthesis halide exchange reaction on Mn²⁺-doped CsPbCl₃ was attempted, but this was only partially successful. The halide exchange of Mn²⁺-doped CsPbCl₃ with Br⁻ using ZnBr₂ salt dissolved in the mixture of hexane and oleylamine as the precursor resulted in not only the exchange of halide but also removal of doped Mn²⁺ ions in the host NCs (Figure 60a).³¹¹ Cation exchange from Pb²⁺ to Mn²⁺ in CsPbBr₃ NCs using MnCl₂ was also attempted by Li *et al.* (Figure 60b).⁶¹² However, this approach also suffered from the halide exchange from Br⁻ to Cl⁻, forming Mn²⁺-doped CsPb(Cl/Br)₃ NCs with mostly Cl⁻

occupying the anion sublattice. Huang *et al.* reported another post-synthesis Mn^{2+} doping method based on halide exchange-driven cation exchange (Figure 60c).⁶¹³ In this method, the addition of $MnCl_2$ solution dissolved in DMF to the colloidal solution of $CsPbBr_3$ NCs in toluene resulted in the production of Mn^{2+} -doped $CsPb(Cl/Br)_3$ NCs. Doping of Mn^{2+} was facilitated by the halide exchange, which was conjectured to be the result of simultaneous opening up of the rigid halide octahedron structure around Pb^{2+} as well as the Pb^{2+} to Mn^{2+} cation exchange. However, the approach has the same limitation of obtaining mixed-halide phase after doping, since using $MnBr_2$ solution did not result in Mn^{2+} doping. Qiao *et al.* and Parobek *et al.* extended the halide exchange-driven cation exchange approach as a method for Mn^{2+} doping by combining photoinduced halide exchange.^{312,615} In this method, halide was provided *in situ* via photoinduced reductive dissociation of the solvent (CH_2Br_2) near the surface of the NCs, and a non-halide Mn^{2+} salt was used as the Mn^{2+} source. This approach was able to dope Mn^{2+} in small $CsPbBr_3$ NCs, however, the intensity of the Mn^{2+} luminescence was relatively low, indicating a lower doping concentration.

In Mn -doped $CsPb(Cl/Br)_3$ NCs with mixed-halide composition, the characteristic Mn^{2+} luminescence is still observed since the band gap of the host NCs is still sufficiently high to enable the sensitization of Mn^{2+} transition. However, the Mn^{2+} emission intensity decreases as the Br^- content increases in the mixed-halide NCs. Initially, this was explained by a work from Meijerink and co-workers attributing the decrease in Mn^{2+} emission to thermally assisted back energy transfer from Mn^{2+} to the host NCs, similar to Mn^{2+} -doped $CdSe$.⁶¹⁶ This point was argued by Gamelin and co-workers and they showed the presence of the exciton emission at 4 K, whereas in Mn^{2+} -doped $CdSe$ the Mn^{2+} emission is only present due to the lack of any thermal-related back energy transfer. The mixed-halide perovskite exhibited a temperature-dependent behavior similar to Mn^{2+} -doped $CsPbCl_3$, which has also a higher energy gap for thermally assisted back energy transfer to occur.⁶¹⁷ Instead, Gamelin and co-workers attributed the change in PL properties to the clustering of Mn^{2+} in the lattice as the anion is exchanged from Cl to Br. They supported this by performing anion exchange from Mn^{2+} -doped $CsPbCl_3$ to Mn^{2+} -doped $CsPb(Cl_{1-x}Br_x)_3$ with TMS-Br while showing the retention of Mn^{2+} emission but the disappearance of the EPR signal (Figure 60d).⁶¹⁴

Another avenue toward post-synthesis doping of Mn^{2+} was reported by Mir *et al.*, who used slightly different solvent conditions and were able to dope Mn^{2+} in $CsPbBr_3$ NCs without concomitant halide exchange.⁶¹⁸ In this modified approach, Mn^{2+} doping was achieved using $MnBr_2$ dissolved in the mixture of toluene and acetone, where $MnBr_2$ and $CsPbBr_3$ can coexist due to moderately polar environment of the mixed solvent. It was conjectured that Mn^{2+} doping under these conditions takes advantage of the dynamic nature of binding of a ligand to adsorb dopants on the surface of NCs and fast halide migration to incorporate dopants into the $CsPbBr_3$ NCs, although the detailed mechanism was not fully understood. Employing the same approach, they were able to synthesize Mn^{2+} -doped $CsPbBr_3$ NCs with different morphologies, including nanocubes and NPLs. In the case of NPLs, sensitized Mn^{2+} luminescence was observed due to the increased band gap from the quantum confinement. Pradhan and co-workers also employed a post-synthetic method to dope $CsPbBr_3$ NPLs by mixing them with $MnBr_2$ in a toluene solution. They have

co-related the local Mn^{2+} halide concentration with the change in emission intensity with dilution and preconcentration by evaporation of the dispersed solvent.⁶¹⁹

Although the earlier attempts to dope Mn^{2+} in $CsPbBr_3$ NCs *via* one-pot hot-injection synthesis only resulted in a NC with enhanced stability but no visible Mn^{2+} luminescence,⁶²¹ Parobek *et al.* developed a direct hot-injection method that produces Mn^{2+} -doped $CsPbBr_3$ NCs *via* a two-step synthesis that exhibit Mn^{2+} luminescence (Figure 61).⁶²⁰ In the first step

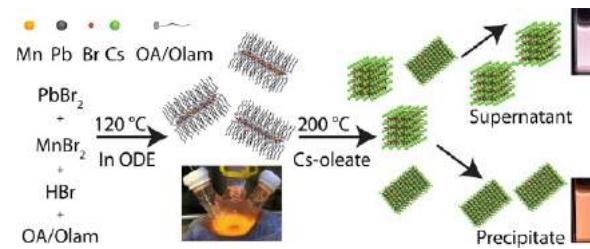


Figure 61. Mn^{2+} doping in $CsPbBr_3$ NCs: Schematic representation of synthesis of Mn^{2+} -doped $CsPbBr_3$ NCs. Image was taken from ref 620. Copyright 2018 American Chemical Society.

of the synthesis, a Mn^{2+} -doped monolayer 2D structure is synthesized ($L_2[Pb_xMn_{1-x}Br_4]$, where L is a ligand) as an intermediate species. The presence of the intermediate 2D structure doped with Mn^{2+} was confirmed by small-angle X-ray diffraction, which revealed the presence of stacked 2D layers with 4.1 nm interlayer spacing. Further confirmation of Mn^{2+} doping within the 2D structure came from the absorption spectrum and photoluminescence excitation spectrum at 620 nm where the Mn^{2+} luminescence is observed. In the second step, the intermediate structure was converted to Mn^{2+} -doped $CsPbBr_3$ NCs by adding Cs-oleate at 200°C. Interestingly, the resulting product was a mixture of Mn^{2+} -doped $CsPbBr_3$ NCs with two different morphologies, *i.e.*, nanocubes (6.5–8.5 nm) and NPLs (~2 nm in thickness), which were separated from each other *via* centrifugation. Since both Mn^{2+} -doped $CsPbBr_3$ NCs have sufficiently high band gap, due to quantum confinement, sensitized Mn^{2+} luminescence was observed in this work.

Mn^{2+} Doping in $CsPbI_3$ NCs. Doping of Mn^{2+} in $CsPbI_3$ NCs has also been reported by several groups. Akkerman *et al.* reported the synthesis of Mn^{2+} -doped $CsPbI_3$ using MnI_2 as an additional reactant added in the hot-injection synthesis of $CsPbI_3$ NCs.⁶⁰⁷ Mn -doped $CsPbI_3$ NCs with ~12 nm size were obtained from this synthesis. Unlike in Mn^{2+} -doped $CsPbCl_3$ and $CsPbBr_3$ NCs, the band gap of $CsPbCl_3$ NCs is smaller than the d–d ligand field transition energy of Mn^{2+} , which prevents sensitization of the Mn^{2+} luminescence. This also makes it more challenging to confirm doping by spectroscopic techniques. On the other hand, the purpose of that work was to stabilize the perovskite phase and prevent its transition to the δ - $CsPbI_3$ non-perovskite phase, as will be discussed later in more detail. In another work, Mir *et al.* reported post-synthesis Mn^{2+} doping using MnI_2 dissolved in methyl acetate as the precursor of Mn^{2+} . In their reaction, doping was achieved at room temperature by mixing the solutions of $CsPbI_3$ NCs and MnI_2 .⁶⁰¹

Sensitized Mn^{2+} Luminescence and Energy Transfer Dynamics. So far, the most studied optical properties of Mn^{2+} -doped $CsPbX_3$ NCs are related to the sensitized Mn luminescence along with the competitive dynamics between

the radiative recombination of exciton and energy transfer to Mn^{2+} . The relative intensities of exciton and Mn^{2+} -dopant emissions depend on various factors, including the doping density, the relative energetics of host NC band gap and the d-d transition of the Mn^{2+} involved in the sensitization, degree of quantum confinement in the host NCs and temperature. While a complete picture of the correlation between these variables and PL intensities has not yet emerged, several recent studies have provided additional insights on the energy-transfer dynamics and microscopic mechanisms based on temperature-dependent transient absorption and photoluminescence, as described below.

For the Mn^{2+} -doped $CsPbX_3$ NCs, Rossi *et al.* performed time-resolved experiments to directly measure the rate of energy transfer instead of estimating it from the luminescence quantum yield and relative intensities of luminescence from the host and Mn^{2+} .⁶²² In their study, the energy-transfer time (τ_{ET}) was obtained by a comparative analysis of the recovery time of the bleach signal at the band-edge in Mn^{2+} -doped and undoped NCs using pump-probe transient absorption spectroscopy. The energy-transfer pathway that exists only in Mn^{2+} -doped NCs was manifested as an additional dynamic component in the bleach recovery of the exciton, as shown in Figure 62. In Mn^{2+} -doped $CsPbCl_3$ nanocubes with an edge

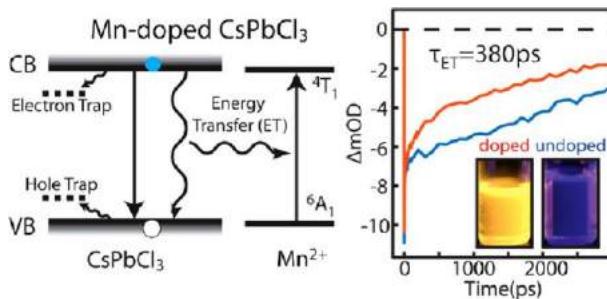


Figure 62. Dynamics of Mn^{2+} -doped $CsPbCl_3$: Scheme of exciton to dopant energy transfer in Mn^{2+} -doped $CsPbCl_3$ NCs and transient absorption data for doped and undoped $CsPbCl_3$. Images were taken from ref 622. Copyright 2017 American Chemical Society

length of 10 nm and a $\sim 0.4\%$ doping concentration, τ_{ET} was determined to be ~ 380 ps.⁶²² Compared to the τ_{ET} value of the previously studied Mn^{2+} -doped CdS/ZnS NCs after correcting for the difference in doping concentration, the τ_{ET} in the Mn^{2+} -doped $CsPbCl_3$ nanocubes is 2–5 times slower. The slower energy transfer in $CsPbCl_3$ NCs compared to II–VI QDs was attributed to the intrinsically weaker exchange interaction among excitons and d electrons of the dopant in $CsPbCl_3$ NCs and the weaker quantum confinement of the host NCs. De *et al.* also performed transient absorption spectroscopy in Mn^{2+} -doped and undoped $CsPbCl_3$ NCs and made a similar observation.⁶²³ They also observed the faster recovery of the bleach at the band-edge in Mn^{2+} -doped NCs reflecting the energy transfer. So far, direct time-resolved studies have been limited to $CsPbCl_3$ NCs with weak confinement. An indirect study on the rate of energy transfer based on relative intensities of exciton and Mn^{2+} PL was performed in $CsPb(Cl/Br)_3$ NCs as a function of the halide composition. In the study by Xu *et al.*, the variation of I_{Mn}/I_{exc} (ratio of Mn^{2+} and exciton photoluminescence intensity) with Br/Cl ratio in the host NCs was systematically studied.⁶¹⁶ An

initial fast increase in the I_{Mn}/I_{exc} with increasing Br^- content is followed by a decrease for higher Br^- contents. The authors explained this observation by a reduced exciton decay rate and faster exciton to Mn^{2+} energy transfer upon Br^- substitution. Clearly, further investigation of other Mn^{2+} -doped $CsPbX_3$ NCs with different halide compositions and varying degrees of quantum confinement is necessary to obtain a better picture of the coupling between the exciton and dopant in this system.

A number of temperature-dependent studies on the intensity and lifetime of exciton and Mn^{2+} photoluminescence were performed by several groups, from which the involvement of a charge-separated state of exciton or trapped exciton in the energy-transfer process was inferred. Yuan *et al.* measured the temperature-dependent exciton and Mn^{2+} PL intensities at 80–300 K.⁶¹⁷ Exciton PL increased with decrease in temperature in this range, whereas Mn^{2+} PL exhibited the opposite behavior (Figure 63). To explain the observed temperature-dependent PL intensities, the authors introduced a thermally activated charge-separated state that is longer-lived than the exciton and that also participates in the energy-

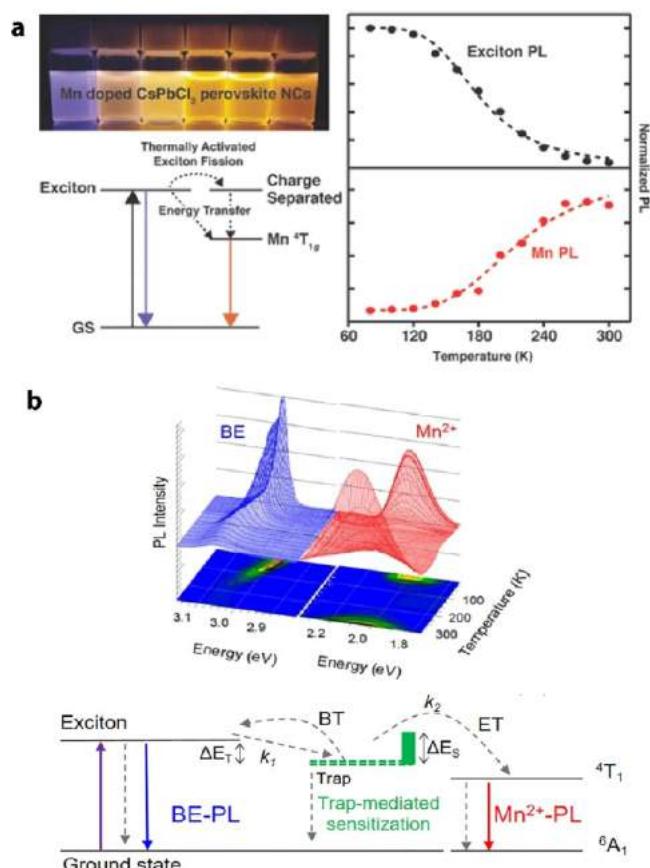


Figure 63. Temperature-dependent PL of Mn^{2+} -doped $CsPbCl_3$ NCs. Temperature-dependent exciton PL and Mn^{2+} PL intensities in Mn^{2+} -doped $CsPbCl_3$ NC films deposited on silicon substrates with 2.4% Mn^{2+} , normalized at 80 K. Energy level diagram describing the energy transfer process via thermally activated charge-separated state is also shown. Taken from ref 617. Copyright 2017 American Chemical Society. (b) 3D plot of PL spectra of the band-edge exciton (BE) and Mn^{2+} luminescence from Mn^{2+} -doped $CsPbCl_3$ NCs. Bottom figure is the Jablonski diagram showing the energy-transfer process through intermediate shallow trap state. Reprinted from ref 624. Copyright 2019 American Chemical Society.

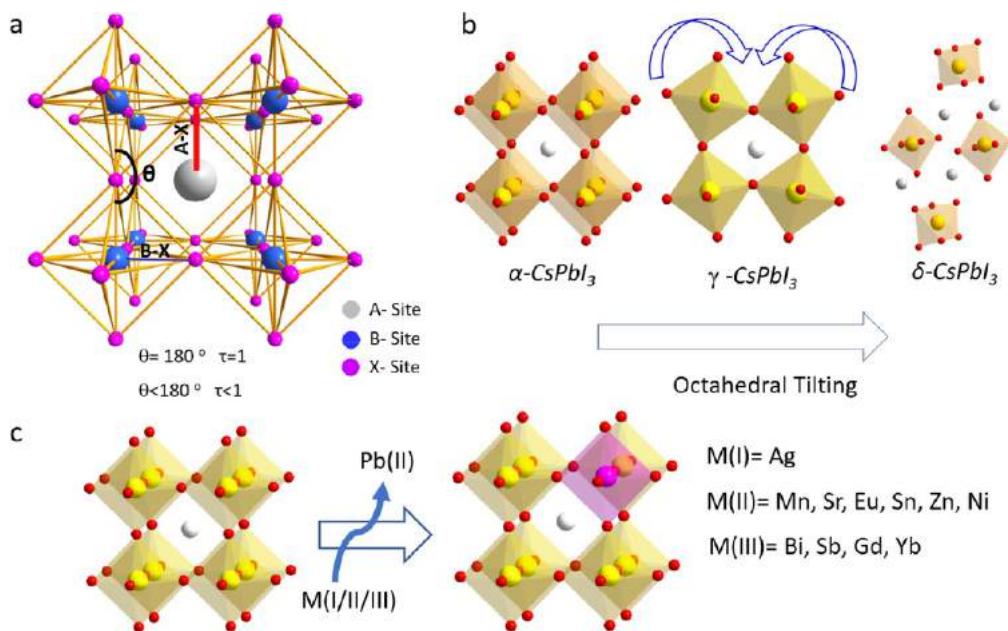


Figure 64. (a) Schematic representation of a typical ABX_3 unit cell showing bond lengths, tilting angle (θ), and relationship of tilting angle (θ) with Goldschmidt tolerance factor (t). Reproduced from ref 625. Copyright 2019 American Chemical Society. (b) Various ABX_3 unit cells with increasing tolerance factor. (c) Schematic illustration of B-site doping with various reported metal ions.

transfer process. In this scheme, the temperature-dependent competition between radiative recombination of exciton and formation of charge-separated state ultimately determined the temperature-dependent competitive kinetics of exciton relaxation and energy transfer. More recently, Pinchetti *et al.* extended the range of temperature down to 5 K and studied the temperature-dependent branching between exciton recombination and energy transfer.⁶²⁴ The noteworthy observation is the reappearance of Mn^{2+} PL intensity below 70 K that increases with decrease in temperature, which contrasts to the trend at the higher temperatures. To explain the more complex temperature dependence of the PL intensities, the authors proposed a two-step process involving the initial localization of band-edge excitons in a shallow trap that mediates the sensitization of the dopants and repopulates the band-edge by thermally activated back-transfer. While this trap-mediated process was considered dominating above 70 K, the authors suggested that the barrierless energy transfer directly from band-edge exciton to Mn^{2+} occurs below 70 K, which explains the reemergence of Mn^{2+} PL at the lower temperatures.

B-Site Doping to Stabilize Red-Emitting $CsPbI_3$ NCs.

The assessment of the Goldschmidt's tolerance factor (t) using ionic radii is very popular among the halide perovskite community, but one must remember that this was initially proposed for oxide and fluoride-based perovskites, for which only ionic interactions can be safely considered. However, in comparison with fluoride, the polarizability of iodide induces a covalent character to the bonding and the traditional calculation of t does not clearly account for the stability of the perovskite system. Travis *et al.* correlated different experimental result to obtain the exact radii, and they found that the radii of $Pb(II)$ in chloride, bromide, and iodide are 0.99, 0.98, and 1.03 Å, respectively, that is, significantly shorter than the Shannon ionic radius (1.19 Å).⁵¹ Hence, they proposed a modified t calculation with the experimentally obtained radii values. After considering all these the calculated t for $CsPbI_3$ is 0.89, which is on the margin of the stable

perovskite structure. In that case, the red emissive α - $CsPbI_3$ NCs degrade into the yellow non-emitting δ - $CsPbI_3$ phase after few days of preparation.

It has been widely reported that the stability of the black perovskite phase of $CsPbI_3$ NCs can be significantly improved by doping or alloying them with a divalent cation of a smaller ionic radius than that of Pb^{2+} , which leads to an increase in t . A schematic of the B-site doping and the various dopant ions studied to date are illustrated in Figure 64c. For instance, Akkerman *et al.* have shown that alloying of α - $CsPbI_3$ NCs with Mn^{2+} leads to a significant enhancement in their stability while preserving the optical features and crystal structure of pristine $CsPbI_3$ NCs.⁶⁰⁷ The authors demonstrated that the $CsPb_xMn_{1-x}I_3$ NCs were stable over a month in either colloidal solution or thin films. The density functional calculations showed that the conduction and valence bands of $CsPbI_3$ are influenced by both s and p orbitals of Pb and I respectively, while the Mn d-states remained far below the conduction band. Hence, Mn^{2+} doping did not alter the band gap or optical features of the pristine NCs. Similarly, alloying $CsPbI_3$ NCs with Sn^{2+} also enhances their stability, but in this case it does influence the band gap of the NCs, hence their optical features.⁵³⁰ As discussed in earlier sections, $CsSnI_3$ is not stable because of the ease of oxidation of Sn^{2+} to Sn^{4+} . Interestingly, the alloyed $CsSn_{1-x}Pb_xI_3$ NCs remained stable for more than 150 days. $CsSnI_3$ and $CsPbI_3$ have band gaps of 1.3 and 1.75 eV, respectively, and their alloyed NCs possess intermediate band gap. These works suggest that the selection of proper B-site dopants remains critical for preserving phase stability, but its influence on the optical properties of the NCs cannot be ignored. In another work, Shen *et al.*⁶²⁶ demonstrated that alloying with Zn^{2+} reduces the nonradiative decay rates by suppressing the defect states in $CsPbI_3$ NCs, and increases the radiative decay rates by enhancing the exciton binding energy of the NCs. Recently, Yao *et al.* reported the use of $Sr(II)$ as a dopant to stabilize cubic- $CsPbI_3$ NCs.⁶²⁷ As the ionic radius of $Sr(II)$ is smaller than that of

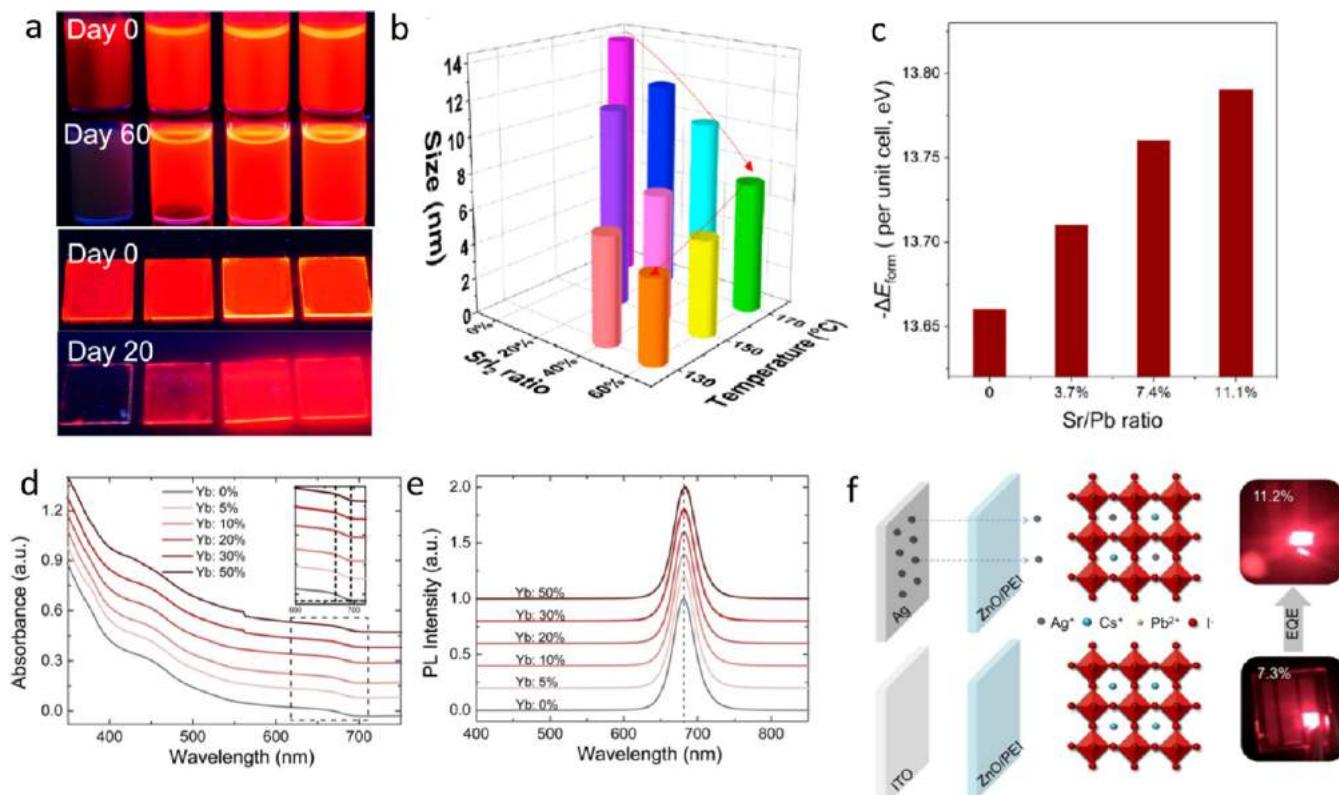


Figure 65. (a) Digital image of films and NC suspension of CsPbI_3 NCs prepared with 0% SrI_2 at 170°C , 40% SrI_2 at 170°C , 60% SrI_2 at 170°C , and 60% SrI_2 at 150°C . (b) Plots showing the change of size of NCs with the amount of SrI_2 introduction at different temperatures. (c) Histogram showing change in formation energy with change in Sr to Pb ratios. Images a–c were obtained from ref 627. Copyright 2019 American Chemical Society. Absorption (d) and PL spectra (e) of CsPbI_3 NCs synthesized at various loadings of Yb. Inset of (d) is the enlarged view of the band-edge of all absorption spectra. The spectra shows that the band gap remains unaltered regardless of the amount of Yb doping. Panels d and e were reproduced with permission from ref 628. Copyright 2019 Royal Society of Chemistry. (f) Films of CsPbI_3 NCs with and without Ag(I) and their respective lighting LEDs. Panel f is reproduced from ref 631. Copyright 2018 American Chemical Society.

$\text{Pb}(\text{II})$, its inclusion in CsPbI_3 NCs leads to the contraction of the crystal lattice and thus improves its phase stability. Figure 65a presents a photograph of the CsPbI_3 NC suspensions and the corresponding films prepared under the addition of different percentages of SrI_2 and the colloidal solutions and films after 60 and 20 days of preparation, respectively. In addition, the average size of the doped CsPbI_3 NCs was found to be dependent on the SrI_2 loading at various temperatures (Figure 65b),⁶²⁷ in analogy with other reports in which the concentration of halide ions in the synthesis is a key parameter for controlling the size of perovskite NCs.^{79,149} To support the experimental findings on increased stability, the authors further computed the formation energy of doped cubic CsPbI_3 NCs, and it increases with increasing the the Sr to Pb ratios, as shown in Figure 65c.

In addition to isovalent doping/alloying, the introduction of heterovalent ions (e.g., Yb(III), Gd(III) and Sb(III)) ions was also explored to stabilize the cubic phase and preserve the red emission of the CsPbI_3 NCs.^{628–630} Figure 65d,e presents the absorption and PL spectra of CsPbI_3 NCs with various amounts of Yb(III) doping. From the band-edge absorption spectra (inset of Figure 65d), the band gap was found to be unchanged regardless of the level of doping. In addition, the authors claimed that the PLQY increased from 75% to 86% with 20% Yb(III) doping, while it decreases at higher amounts of doping. The authors attributed this enhancement to reduction in the density of defects and trap states created by

surface and lattice vacancies.⁶²⁸ In another work, Lu *et al.* found spontaneous Ag(I) doping in CsPbI_3 film when an Ag film was used as an electrode in place of ITO in an LED device.⁶³¹ In addition, they claimed that the Ag (I) ions passivate the CsPbI_3 NC surface, leading to the increase of EQE from 7.3 to 11.2% using Ag electrode in the LED device (Figure 65f).

While analyzing the various reports on doping metal ions to achieve phase stabilization of red-emitting perovskite CsPbI_3 , Behera *et al.* found a correlation between temporal stability (either in solution or in the film) and size of the B-site (*i.e.*, the Pb^{2+} site) dopant ions of CsPbI_3 . A list of ions used as dopants, along with the available values of the corresponding Shannon radii, is provided in Figure 66a. Among these, Ni(II) has the lowest Shannon radius, and it was found that CsPbI_3 NCs doped with this ion exhibited relatively longer stability.⁶³² Photographs of the colloidal suspensions of Ni(II)-doped and undoped CsPbI_3 NCs are shown in Figure 66b: the suspension containing undoped NCs turned yellow after 5 days, while the one containing the Ni(II)-doped NCs preserved its red color even after 45 days of aging. Figure 66c,d presents the absorption and PL spectra of suspensions of the undoped and Ni(II)-doped NCs (as-synthesized and aged). Both suspensions are red-emitting soon after their synthesis. However, while the undoped sample becomes non-emissive after 5 days (Figure 66d), the Ni(II)-doped sample remains strongly red-emitting even after 45 days. The phase change of

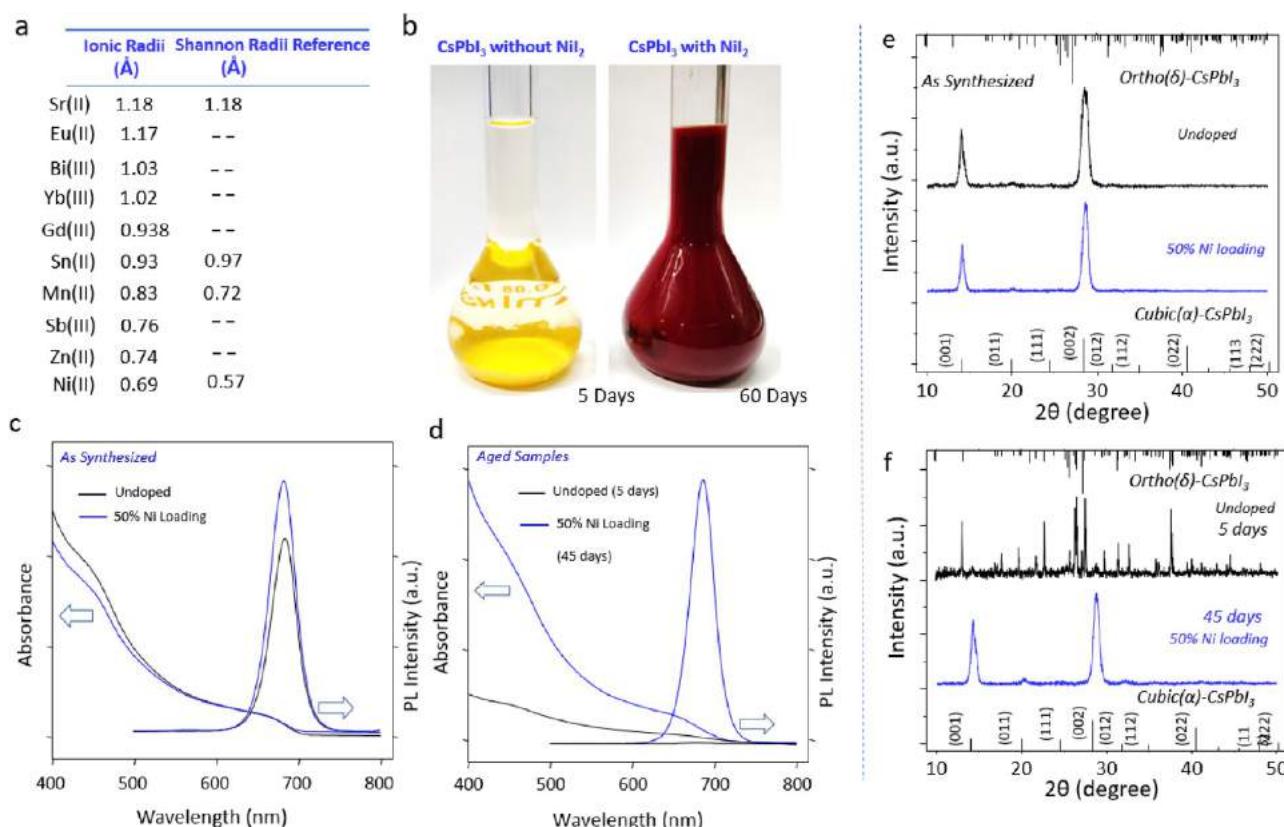


Figure 66. (a) Table showing ionic and Shannon radii of various metal ions used for stabilizing CsPbI_3 NCs. (b) Photographs of CsPbI_3 NCs dispersions without and with NiI_2 addition in the respective syntheses. (c,d) Time-dependent absorption and PL spectra of as-synthesized and aged CsPbI_3 NCs with and without NiI_2 addition. (e,f) Powder X-ray diffractions of as-synthesized and aged samples with and without Ni-incorporated CsPbI_3 NCs. These images were obtained from ref 632. Copyright 2019 American Chemical Society.

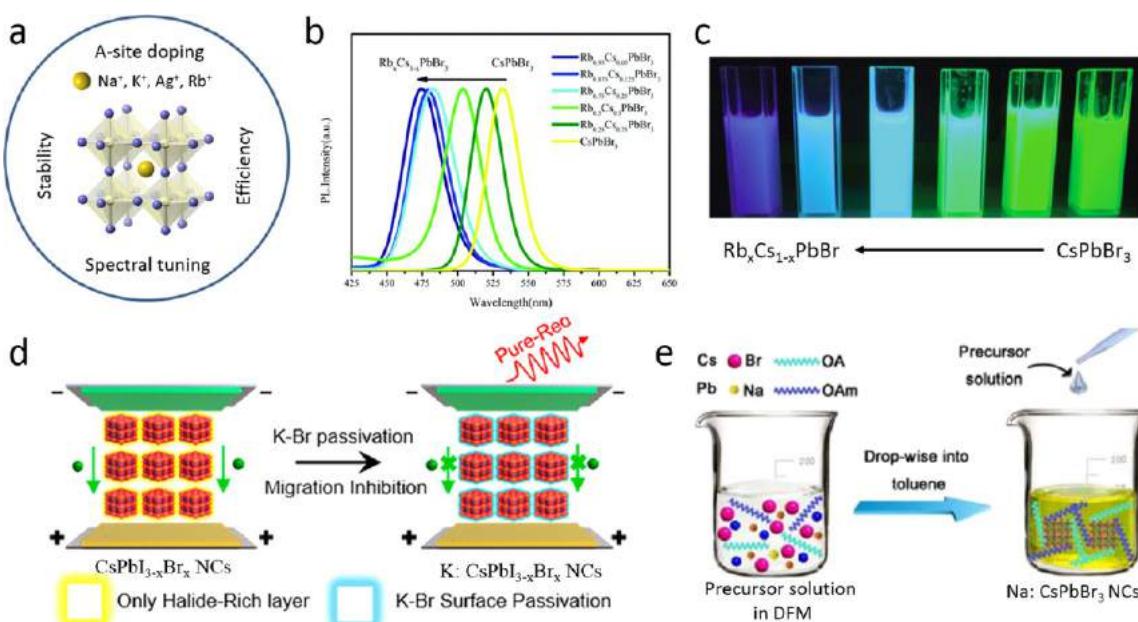


Figure 67. (a) Schematic illustration of the perovskite cubic crystal structure with possible A-site dopants including Na^+ , K^+ , Ag^+ , and Rb^+ . Through doping, enhanced stability, device efficiency, and spectral tuning have been achieved. (b) Photoluminescence spectra of $\text{Rb}_{x}\text{Cs}_{1-x}\text{PbBr}_3$ colloidal solutions under 365 nm excitation. (c) Photograph of the colloidal solutions of Rb^+ -doped CsPbBr_3 perovskite NCs under UV light illumination. Panels b and c are reproduced with permission from ref 583. Copyright 2018 Royal Society of Chemistry. (d) Schematic illustration of doping K^+ into $\text{CsPbI}_{3-x}\text{Br}_x$ NCs by surface passivation to improve red photoluminescence. Reproduced from ref 400. Copyright 2020 American Chemical Society. (e) Schematic illustration of the synthesis of the Na^+ -doped CsPbBr_3 NCs by ligand-assisted reprecipitation approach. Reproduced from ref 637. Copyright 2019 American Chemical Society.

the undoped sample after 5 days can be clearly seen in the powder X-ray measurements (Figure 66e,f).

As discussed above, most reports suggest that the doping or alloying in CsPbI_3 NCs improves the phase stability, and thus the optical quality and stability. It has also been claimed that the doping removes nonradiative traps. In most cases, it was speculated that the divalent dopants occupy Pb positions of the crystal lattice. In some reports, theoretical supports were also provided for their experimental observations. However, there is no clear microscopic evidence for solid for doping of B-site to date. On the other hand, in most studies, respective iodide precursors were introduced for B-site doping, and this could lead to iodide-rich condition in the synthesis. For instance, Liu *et al.* promoted iodide-rich conditions in a typical CsPbI_3 NC synthesis using GeI_2 as an additional Iodide source.⁶³³ The authors claimed that the excess iodide in the reaction helped to stabilize the CsPbI_3 NCs, however, unlike other bivalent metals Ge was not incorporated in the NC lattice. A similar observation was reported by Woo *et al.* using ZnI_2 as an additional iodide precursor in the CsPbI_3 NC synthesis.³⁹⁷ On the other hand, Imran *et al.*¹⁷⁸ and Cai *et al.*¹⁶⁸ separately reported the use of non-halide Pb and Cs precursors in the perovskite NC synthesis, in which the reaction was triggered by benzoyl iodide and trimethylsilyl iodide as iodide precursors, respectively. In both cases, stable CsPbI_3 NCs were prepared. These results put under discussion the real need of doping in order to improve the stability of black-phase CsPbI_3 NCs by replacing Pb(II) by mono-, di-, and trivalent dopant ions. Hence, in-depth experimental and theoretical studies are needed for better understanding and concluding the role of dopants in the stabilization of black-phase, red-emitting CsPbI_3 NCs.

Apparent A-Site Doping. In addition to the bivalent metal cation dopants discussed above, several monovalent cation dopants such as Rb^+ , Na^+ , K^+ , and Ag^+ are also being intensively investigated to enhance the stability as well as photoluminescence efficiency of perovskite NCs (Figure 67a).^{573,634} It has been claimed that these dopants occupy A-sites of perovskite NC lattice. The selection of dopants is generally inspired from the previous research on perovskite solar cells, in which perovskite films were doped with various monovalent cations to improve their power conversion efficiency and stability.^{108,573,634,635} The phase stability of perovskites with specific monovalent cations depends on their size and thus tolerance factor as discussed above.⁶³⁵ For instance, Cs^+ , MA^+ , and FA^+ ions fit well into the A-site of the lead iodide perovskite structure (Cs^+ “less” well than MA^+ and FA^+ , as discussed in the previous sections), while small metal ions such as Li^+ , Rb^+ , Na^+ , and K^+ cannot stabilize the perovskite structure due to a low tolerance factor.⁶³⁵ Interestingly, doping these small cations into perovskite NCs improves their optical properties and phase stability. Saliba *et al.*⁶³⁵ showed the incorporation of small and oxidation-stable Rb^+ into mixed cation perovskite (CsMAFA) films to create photoactive perovskite films with excellent material properties. Interestingly, Rb^+ incorporation does not alter the valence band position of the host perovskite. They have showed that the Rb^+ doping into perovskites leads to higher phase stability and more reproducible power conversion efficiencies (PEC). Further studies revealed that Rb^+ incorporation can also enhance the performance of the corresponding light-emitting diodes.⁶³⁶

Recently, the concept of Rb^+ doping into bulk perovskites has been extended to perovskite NCs as well.^{583,638–641} For instance, Wu *et al.*⁵⁸³ synthesized Rb^+ -doped CsPbBr_3 perovskite NCs with different ratios of Rb/Cs by the hot-injection method. It was found that the band gap gradually increases and thus the photoluminescence blue shifts with the increase of the Rb/Cs ratio (Figure 67b,c). It is very interesting that the $\text{Rb}_{x}\text{Cs}_{1-x}\text{PbBr}_3$ colloidal solution exhibit blue photoluminescence with increasing the Rb^+ dopant concentrations. The authors attributed the increase in the band gap to changes in the valence and conduction bands caused by the decrease of in-plane Pb–Br–Pb bond angle of the $[\text{PbBr}_6]$ octahedron by the replacement of Cs^+ with small Rb^+ ions that does not fit well into perovskite lattice due to low tolerance factor.⁵⁸³ A similar blue shift in photoluminescence was observed for $\text{Rb}_{x}\text{Cs}_{1-x}\text{PbBrI}_2$ NCs with increasing ratio of Rb/Cs .⁶⁴² Furthermore, Rb^+ ions can also be doped into perovskite nanoplates of different thicknesses to achieve tunable emission (green–sky blue–blue) with PLQY over 60%, as shown by Sargent and co-workers.⁶⁴⁰ The fabrication of sky-blue and deep-blue LEDs has been demonstrated using these mixed cation $\text{Rb}_{x}\text{Cs}_{1-x}\text{PbBr}_3$ nanoplates, and they exhibit relatively high thermal stability and operational stability. Despite these few studies, the location (either on the surface or inside the lattice) of Rb^+ ions in perovskite lattice is still unclear. Very recently, Etgar and co-workers⁶³⁸ performed EDS analysis on atomically resolved HAADF-STEM images of $\text{Rb}_{x}\text{Cs}_{1-x}\text{PbBr}_3$ NCs to understand the position of Rb^+ ions in the lattice. They claimed that at medium dopant concentrations the Rb^+ ions stays in the core region, while the Cs atoms are preferentially located in the shell region, forming core–shell like structures. However, at high Rb^+ dopant concentrations a phase separation of Rb^+ occurs within the perovskite NCs, because Rb atoms cannot form the perovskite phase. In contrast, Kubicki *et al.*⁶⁴³ performed ^{14}N solid-state magic-angle spinning (MAS) NMR to probe the compositions of mixed cation (Cs , Rb , K , MA, FA) perovskites and they found no signs of Rb or K incorporation into the bulk perovskite lattice. From an X-ray photoelectron spectroscopy study, they found that the surface of perovskites has rubidium-rich phases, which can acts as a passivation layer for the perovskites.

In addition, other alkali metal ions including K^+ and Na^+ are also gaining attention as potential dopants for perovskite NCs to enhance their stability and photoluminescence efficiency. For instance, Huang *et al.*³⁵³ reported a post-synthetic surface treatment of CsPbBr_3 perovskite NCs with K-oleate to improve their PLQY and photostability. After K^+ treatment, the NC films retained their original photoluminescence intensity even after 150 h of illumination. However, it is not clear whether the K^+ ions just passivated the NC surface or it diffused into the perovskite lattice. Similarly, $\text{CsPbI}_{3-x}\text{Br}_x$ NCs were treated with K-oleate to enhance red photoluminescence, as demonstrated by Yang *et al.* (Figure 67d).⁴⁰⁰ The addition of K-oleate led to the formation of KBr on the $\text{CsPbI}_{3-x}\text{Br}_x$ NC surface, which then passivated the NC surface effectively to obtain PLQY over 90% (Figure 67d). More importantly, the K^+ ions were able to protect the NC surface from halide segregation, and the LED made using these NCs exhibited stable electroluminescence and high brightness. On the other hand, Na^+ ions were incorporated into colloidal CsPbBr_3 NCs by ligand-assisted reprecipitation approach, as shown in Figure 67e.⁶³⁷ It was found that the Na^+ -doped CsPbBr_3 NCs exhibit

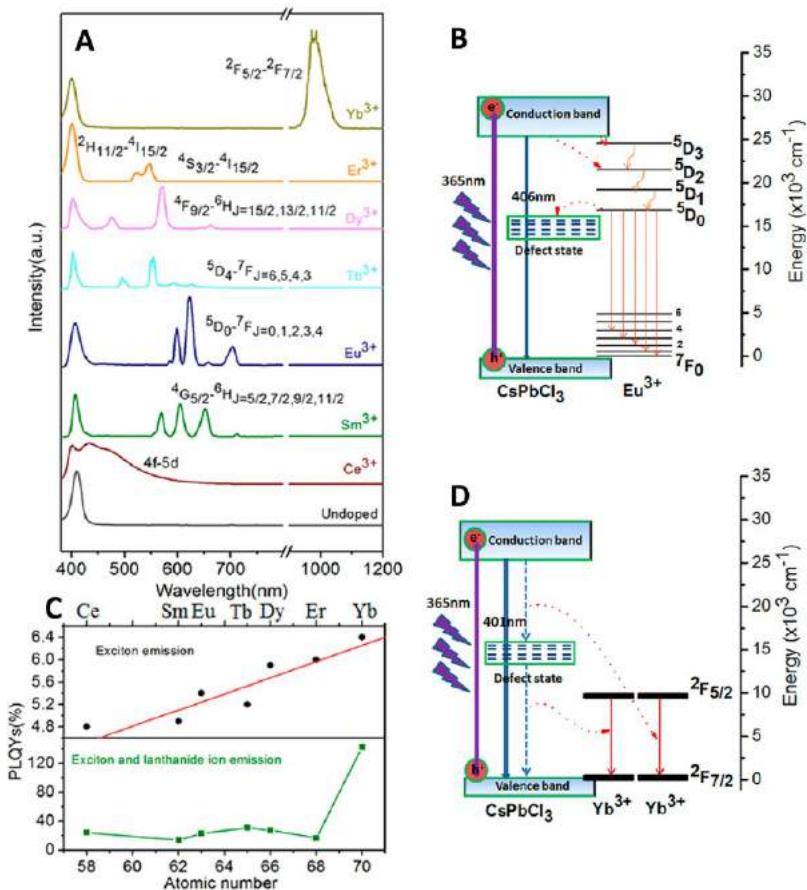


Figure 68. (A) Emission spectra of CsPbCl₃ NCs doped with different lanthanide ions. (B) Proposed energy level diagram for Eu³⁺-doped CsPbCl₃ NCs showing a possible photoluminescence mechanism. (C) Photoluminescence quantum yields for excitonic (top) and overall (exciton + Ln³⁺, bottom) emission features. (D) Proposed energy-level diagram for Yb³⁺-doped CsPbCl₃ NCs showing a possible mechanism for quantum cutting *via* stepwise energy transfer involving a deep (mid-gap) defect state. Adapted from ref 663. Copyright 2017 American Chemical Society.

better color purity and higher PLQY. This was attributed to the reduction of nonradiative trap centers in NCs by Na⁺ passivation. In addition, a gradual blue shift in the emission peak was observed with an increasing Na⁺ dopant concentration similar to Rb⁺-doped perovskite NCs. More importantly, the Na⁺-doped CsPbBr₃ NCs had enhanced stability against ultraviolet light, heat, and moisture compared to pure CsPbBr₃ NCs, and thus the white LEDs fabricated using these Na:CsPbBr₃ NCs as phosphors showed superior stability even under continuous runs for over 500 h.⁶³⁷ In another report, Chen *et al.*⁶⁴⁴ demonstrated the *in situ* incorporation of Na⁺ ions into CsPbBr₃ NCs prepared directly on a substrate using NaBr additive in the precursor solution. The authors claimed that the added NaBr passivates the NC defects and also improves the conductivity of the films. More importantly, the green LEDs fabricated using Na:CsPbBr₃ exhibited a maximum EQE of 17.4%, which is higher than the values measured on the LEDs prepared using pure CsPbBr₃ NCs (EQE ~ 12%).⁶⁴⁴ Based on the above discussed examples, it is clear that doping perovskite NCs with smaller monovalent cations improves their stability as well as PLQY, and thus the efficiency of LEDs. Despite these early studies, the mechanism of doping is rather unclear and the question regarding the position of dopants in the NCs (surface or inside crystal lattice) is yet to be addressed satisfactorily. Addressing this question requires a detailed analysis of atomically resolved

HAADF-STEM images, but this is challenging, as the amount of dopants is rather small and perovskite NCs are quite prone to damage induced by electron beam irradiation. In addition, the relation between the concentration of dopants and the emission efficiency is yet to be investigated in detail. It is likely that, in all studied cases, there is an optimum dopant concentration that maximizes the PLQY, past which any additional doping may start actually degrading the emission efficiency.

Lanthanide-Doped Perovskite Nanocrystals. Lanthanide ions are widely used as luminescence activators in inorganic materials.^{645,646} For example, the spectral conversion phosphors in fluorescent lighting use lanthanides as activators to emit visible photons following absorption of high-energy photons by the host material (either the host lattice itself or an additional “sensitizer” impurity). Trivalent lanthanides (Ln³⁺) are particularly excellent in this role. The high shielding of their 4f valence orbitals results in sharp-line f-f emission that is relatively insensitive to the crystalline field around the lanthanide. Furthermore, white light of almost arbitrary color temperature can be generated by combining several lanthanides.

The f-f internal transitions of the lanthanides are parity-forbidden and are only weakly coupled to lattice distortions that might relax this forbiddenness. Their radiative lifetimes are therefore often extremely long (e.g., milliseconds). In

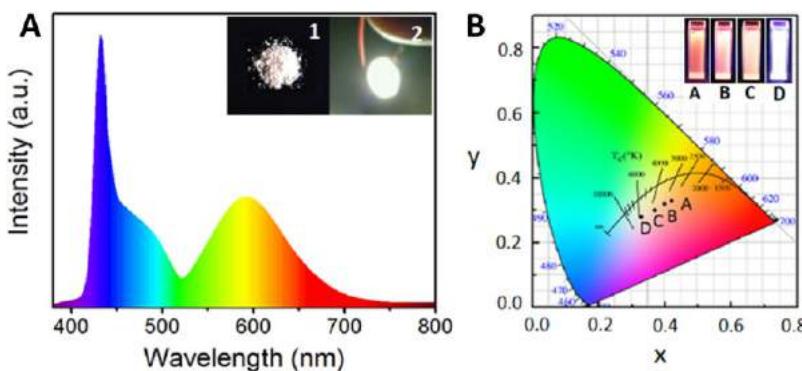


Figure 69. (A) Emission spectrum of a WLED based on 2.7% Ce^{3+} /9.1% Mn^{2+} -codoped $\text{CsPb}(\text{Cl}_{0.6}\text{Br}_{0.4})_3$ nanocrystals pumped by an underlying UV diode. Inset 1 shows the powdered phosphor composite made by mixing the NCs with polystyrene, and inset 2 shows a photograph of the operating device prepared by depositing the phosphor composite onto a 365 nm chip. (B) CIE chromaticity coordinate plot for WLEDs using Ce^{3+} / Mn^{2+} codoped $\text{CsPb}(\text{Cl}_{1-x}\text{Br}_x)_3$ NC phosphors [A(0.42, 0.33), B(0.39, 0.32), C(0.37, 0.30), and D(0.33, 0.29)]. The inset shows photographs of the PL from colloidal 2.7% Ce^{3+} /9.1% Mn^{2+} -codoped $\text{CsPb}(\text{Cl}_{1-x}\text{Br}_x)_3$ NCs with different values of x under 365 nm excitation. Adapted from ref 652. Copyright 2018 American Chemical Society.

crystalline or amorphous matrices with only low-energy vibrations, these ions frequently show very large photoluminescence quantum yields. In a minority of cases, the optical spectroscopy of the lanthanides is dominated not by f-f transitions but rather by f-d transitions. These specific cases include Ce^{3+} and divalent lanthanides, most commonly Eu^{2+} . These f-d transitions are parity allowed, and because of the much greater interaction of the 5d orbitals with the surrounding environment, they are vibronically broadened and their energy is more sensitive to the specific ligand-field environment.

In fluorescent lighting, the phosphor matrices are generally oxides (e.g., Eu^{3+} -doped Y_2O_3 red phosphor) that are robust under the very short wavelength excitation of the mercury gas discharge (254 nm), and the materials need to absorb strongly at these short wavelengths. For other applications, greater visible-light absorption is desirable. Lanthanide-doped perovskite NCs have recently begun attracting broad attention as candidates for visible-light sensitized phosphors.^{580,618,629,647–659,661–663,1354} In contrast with the extensively studied Ln^{3+} -doped fluoride NCs used as upconversion phosphors (e.g., $\text{Ln}^{3+}\text{:NaYF}_4$, $\text{Ln}^{3+}\text{:LaF}_3$, etc.),^{664–666} Ln^{3+} emission in lead-halide perovskite NCs is generated by direct excitation of the semiconductor band-to-band transitions, which have oscillator strengths $\sim 10^5$ times greater than those of the Ln^{3+} f-f transitions. Additional materials with distinctive spectral characteristics have been created by combining the energy-tunable light-harvesting capabilities of metal-halide perovskite NCs with the excellent radiative properties of lanthanide dopants. These materials could be promising for applications such as solar spectral conversion and other related technologies.

Lanthanide-doped lead-halide perovskite NCs appeared in 2017, when the Song group surveyed a series of Ln^{3+} -doped CsPbCl_3 and anion-alloyed $\text{CsPb}(\text{Cl}_{1-x}\text{Br}_x)_3$ NCs involving the entire series of trivalent lanthanide ions.^{661,663} Figure 68a shows the overview figure from one of these studies, organized from top to bottom according to decreasing 4f electron count of the Ln^{3+} dopant in CsPbCl_3 NCs and referenced to the undoped CsPbCl_3 spectrum. A few aspects of these data are notable. First, in each case (except Ce^{3+}), the PL spectrum shows both excitonic PL and the characteristic f-f emission features of the lanthanide known from previous studies in

analogous chloride host lattices. The Ce^{3+} -doped NCs show broad emission near the perovskite band gap, attributed to the well-known f-d emission of this ion. For most cases, the sensitization scheme was considered to involve perovskite photoexcitation followed by nonradiative relaxation within the 4f manifold of excited states until a sizable energy gap was reached, at which point f-f emission is observed (Figure 68b).⁶⁶³

The Ln^{3+} PL sensitized by semiconductor photoexcitation has resulted in the use of such Ln^{3+} -doped NCs in numerous phosphor applications, including lighting or display technologies, near-IR optics, and telecommunications. For example, the Song group subsequently demonstrated the use of CsPbCl_3 and $\text{CsPb}(\text{Cl}_{1-x}\text{Br}_x)_3$ NCs codoped with pairs of impurity ions, e.g., Ce^{3+} / Mn^{2+} , Ce^{3+} / Eu^{3+} , Ce^{3+} / Sm^{3+} , Bi^{3+} / Eu^{3+} , and Bi^{3+} / Sm^{3+} , as spectral converters for white-light generation.⁶⁵² Both ions in these pairs can be sensitized by the host NC, and they function roughly independently of one another, such that color rendering can be optimized by controlling the relative and absolute concentrations of each dopant (Figure 69). Particularly efficient white-light emission was achieved with Ce^{3+} / Mn^{2+} codoping of $\text{CsPb}(\text{Cl}_{0.6}\text{Br}_{0.4})_3$ NCs. These NCs showed PLQYs of $\sim 75\%$ and luminous efficiencies as high as 51 lm/W with good color rendering (~ 89) when pumped at 365 nm from a UV LED chip. These performances demonstrate the lanthanide-doped perovskite NCs' potential as promising alternatives to undoped NCs or other phosphors for lighting applications.

A second notable feature of the data in Figure 68a emerged from PLQY measurements (Figure 68c). For each dopant except Yb^{3+} , the PLQY was modest, summing to a combined value of $\sim 25\%$ split between the exciton and the visible lanthanide transitions. For Yb^{3+} , however, the PLQY appeared to exceed 100%, reaching a value of $\sim 127\%$ for the f-f transition and $\sim 20\%$ for the exciton in the NCs shown in Figure 68a. PLQYs over 100% in Yb^{3+} -doped crystals are rare but not unknown.^{667–669} The phenomenon, referred to as “quantum cutting”, has generally involved participation of pairs of Ln^{3+} ions with matched energy levels, such as one Pr^{3+} + two Yb^{3+} ions. In this case, it was proposed⁶⁶³ that the process requires only Yb^{3+} and the semiconductor NC, involving the suggested stepwise energy transfer shown in Figure 68d. Although the precise microscopic mechanism of quantum

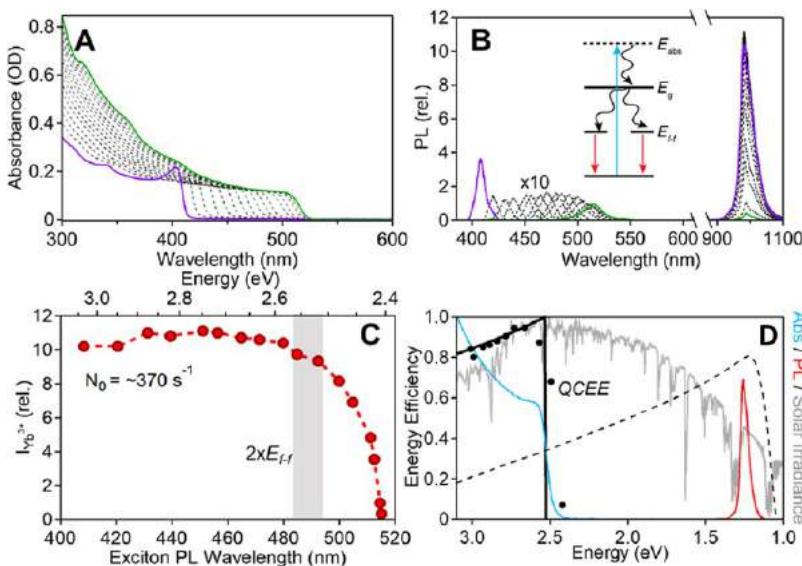


Figure 70. (A) Absorption spectra of 7.7% Yb³⁺:CsPb(Cl_{1-x}Br_x)₃ NCs monitored during anion exchange from Yb³⁺:CsPbCl₃ (purple) to Yb³⁺:CsPbBr_x (green). (B) PL spectra collected *in situ* during the reaction of panel A. PL spectra were measured using a constant NC excitation rate. The inset illustrates the quantum-cutting process. (C) Plot of the Yb³⁺ $^2\text{F}_{5/2} \rightarrow ^2\text{F}_{7/2}$ PL intensity *vs* the exciton PL wavelength, from the spectra in panel B. The gray shaded area marks approximately twice the Yb³⁺ $^2\text{F}_{7/2} \rightarrow ^2\text{F}_{5/2}$ absorption onset ($2 \times E_{\text{f-f}}$) estimated from the PL spectra, *i.e.*, the anticipated energy threshold for quantum cutting in these materials below which energy conservation cannot be maintained. (D) Data from a second experiment like panel C, plotted as the quantum-cutting energy efficiency (QCEE) *vs* E_{abs} (black circles). The black curve plots the idealized QCEE for band-gap-optimized Yb³⁺:CsPb(Cl_{1-x}Br_x)₃ NCs ($x \sim 0.75$, solid black curve). These NCs had a measured PLQY approaching 200%. For comparison, the energy-conversion efficiency of a typical c-Si photovoltaic cell (dashed black), the AM1.5 solar spectral irradiance (gray), and the absorption (blue) and PL spectra (red) of the Yb³⁺:CsPb(Cl_{1-x}Br_x)₃ NCs are also plotted. Reprinted from ref 659. Copyright 2019 American Chemical Society.

cutting remains uncertain at this time, quantum cutting in Yb³⁺-doped CsPbX₃ NCs has now been observed in multiple laboratories, and it represents a major direction in the doping of NCs.

The Song group's synthesis of Ln³⁺-doped CsPbX₃ NCs involved the injection of cation precursors into organic solutions of anions at elevated temperatures (≥ 200 °C), akin to popular procedures for preparing undoped perovskite NCs. An alternative "inverted" approach involving injection of trimethylsilyl halide (TMS-X) precursors into organic solutions of the cation precursors was explored by the Gamelin group: they found that higher Yb³⁺ solubilities could be achieved by this approach, and that the resulting NCs showed correspondingly improved spectroscopic properties, specifically in the form of greater reduction of excitonic photoluminescence and greater Yb³⁺ f-f PLQYs, now approaching 200%.⁶⁵⁰ Other methods for doping Yb³⁺ into perovskite NCs have also been explored. The Nag group demonstrated post-synthetic doping of Yb³⁺ into not just CsPbCl₃ NCs but also into NPLs of both CsPbBr_x and CsPbI_x composition.⁶¹⁸ Yb³⁺ doping was achieved by an interesting post-synthetic cation-exchange strategy, in which Yb(NO₃)₃ dissolved in a mixture of methyl acetate/toluene was added to NC dispersions under continuous stirring for only 1 min, followed by washing using MeOAc as the antisolvent. The process is thus analogous to that recently explored for post-synthetic Mn²⁺ doping of lead-halide perovskite NCs,^{613,670} but now involving Ln³⁺ ions. This interesting chemistry reflects the extreme fluidity of the perovskite lattice, and the ability to drive cation exchange reactions at room temperature. It is unclear whether these materials made by post-synthetic cation exchange also show the very high PLQYs of those made at high temperature, but future comparative studies could shed some insight into the

participating defect structures if temperature is an important contributor to their formation or stability.

The Gamelin group proposed a concerted rather than stepwise mechanism for the microscopic quantum-cutting process.⁶⁵⁰ They observed picosecond exciton depletion associated with Yb³⁺ doping, which appeared too rapid for normal energy transfer to Ln³⁺ ions, and hence the participation of a dopant-induced defect state was hypothesized. In this mechanism, energy is first transferred to this defect state, where it subsequently bifurcates to excite two Yb³⁺ ions simultaneously. The hypothesis of a participating shallow dopant-induced defect state is supported by the observation of similar rapid exciton depletion as well as near-band-edge trap-state emission when Yb³⁺ is replaced by spectroscopically inactive Ln³⁺ ions (*e.g.*, La³⁺).⁶⁵⁰ Time-resolved measurements have confirmed the presence of an intermediate state, showing a *ca.* 7 ns rise time of Yb³⁺ photoluminescence at room temperature.¹³⁵¹ Beyond this, the microscopic details remain unclear. Because no mid-gap intermediate state is involved, the excitations of the two Yb³⁺ ions must be correlated and this mechanism therefore predicts correlated emission from these two Yb³⁺ ions, but such correlation remains to be demonstrated. The Gamelin group also noted that the excess charge of Yb³⁺ requires compensation and speculated that this compensation may be accomplished by substituting three Pb²⁺ ions with only two Yb³⁺ ions, thereby creating a Pb²⁺ vacancy (V_{Pb}), by analogy to the well-known McPherson pair motif in related metal-halide lattices.⁶⁵⁰ Computational work has suggested that a bent charge-neutral Yb-Cl-V_{Pb}-Cl-Yb defect cluster could indeed give rise to such a concerted energy transfer, and has identified accumulation of charge density on neighboring Pb²⁺ ions as important in the microscopic energy-transfer mechanism.¹³⁵⁵

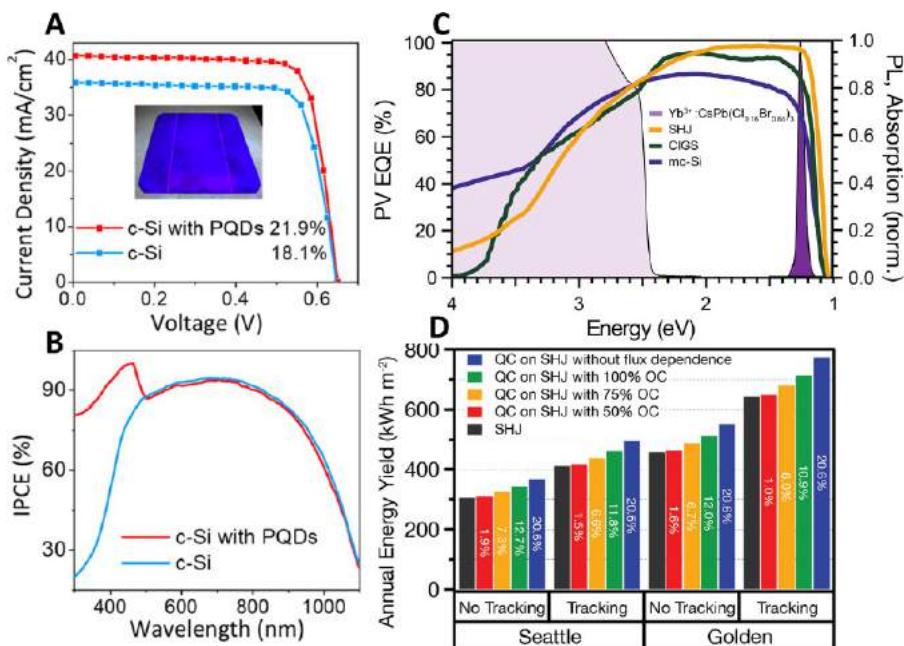


Figure 71. (A) J – V curves of a single-crystal silicon solar cell with and without a coating of Yb^{3+} (6%)– Pr^{3+} (4%)– Ce^{3+} (3%)-tridoped $\text{CsPb}(\text{Cl}_{0.33}\text{Br}_{0.67})_3$ NCs, showing an increase in power-conversion efficiency from 18.1 to 21.9% upon addition of the NCs. (B) IPCE (EQE) curves of a single-crystal silicon solar cell with and without a coating of Yb^{3+} (6%)– Pr^{3+} (4%)– Ce^{3+} (3%)-tridoped $\text{CsPb}(\text{Cl}_{0.33}\text{Br}_{0.67})_3$ NCs, showing enhancement at short wavelengths where the NCs absorb. (C) EQE characteristics of Si heterojunction (SHJ), CIGS, and multicrystalline Si photovoltaics and the absorption and near-infrared (~ 1.26 eV) emission of $\text{Yb}^{3+}:\text{CsPb}(\text{Cl}_{0.16}\text{Br}_{0.84})_3$ quantum cutters, showing the excellent match of the quantum-cutter absorption and photoluminescence with the solar cell response curves, particularly for red-sensitive SHJ. (D) Areal annual energy production yield of a $\text{Yb}^{3+}:\text{CsPb}(\text{Cl}_{1-x}\text{Br}_x)_3$ /SHJ QC/PV device with and without 2-axis tracking mechanisms and for different efficiencies of optical coupling, including the effects of flux-dependent PLQY. Relative percentage increases are labeled on each bar. Results are presented for two geographic locations in the United States: Seattle, WA, and Golden, CO. Panels A and B are reprinted from ref 661. Copyright 2019 American Chemical Society. Panels C and D are reprinted with permission from ref 657. Copyright 2019 Royal Society of Chemistry.

A second important observation came from experiments using post-synthetic anion-exchange chemistries to tune the band gap of Yb^{3+} -doped perovskite NCs.⁶⁵⁹ Figure 70 summarizes the results of one set of measurements that began with Yb^{3+} -doped CsPbCl_3 NCs. Figure 70a shows that substoichiometric titrations of the reactive bromide precursor TMSBr narrowed the perovskite band gap, ultimately reaching ~ 515 nm at complete anion exchange to form Yb^{3+} -doped CsPbBr_3 . Figure 70b plots the excitonic and Yb^{3+} PL spectra for each $\text{CsPb}(\text{Cl}_{1-x}\text{Br}_x)_3$ composition within this series, and Figure 70c summarizes these results by plotting the Yb^{3+} PL intensity *versus* the exciton PL wavelength. These data show that the Yb^{3+} PL intensity remains essentially constant with added bromide until E_g reaches approximately 2 times the f-f energy (gray bar in Figure 70c), at which point the PL drops precipitously. Further experiments showed that the PL recovered upon reverse anion exchange, following much the same trajectory.⁶⁵⁹ These results verify the origin of this Yb^{3+} PL as coming from a 2-for-1 quantum-cutting process. Moreover, these results demonstrate an extremely high quantum-cutting *energy efficiency* (QCEE) of the sensitized PL process, quantified as $\text{QCEE} = \frac{E_{\text{PL}}}{E_{\text{abs}}} \Phi \approx \frac{1.267 \text{ eV}}{E_{\text{abs}}} \Phi$. Figure 70d plots data from another experiment like that in Figure 70c, but now representing the data as the QCEE *versus* absorption threshold energy. This representation shows that experimental QCEEs exceeding 90% can be obtained, *i.e.*, only a very small portion of the energy from the absorbed photon is lost as heat, whereas the vast majority is re-emitted in the near-infrared.

This value can be contrasted with the $\sim 25\%$ energy efficiency of a high-efficiency silicon heterojunction solar cell converting the same blue photon (dashed line in Figure 70d). These results have major significance for potential applications of these materials as spectral conversion layers in photovoltaics; in addition to demonstrating optimization of the band gap for minimal thermalization loss, these results show that the emitted light is well-matched to the absorption onset of red-sensitive Si photovoltaics (Figure 70d).

To further exploit the quantum-cutting properties, the Song group has developed a series of bi- and tridoped lead-halide perovskite NCs incorporating additional amounts of Pr^{3+} and Ce^{3+} , by analogy to more traditional quantum-cutting compositions.^{647,661} Codoping is achieved by hot injection with subsequent anion exchange using PbX_2 to tune the energy gap. Pr^{3+} and Ce^{3+} both possess excited states at energies close to the perovskite energy gap, and time-resolved PL measurements showed participation of these ions, which dramatically slowed the arrival time of the energy in the Yb^{3+} ions, as detected by time-resolved PL.⁶⁶¹ Maximum PLQYs of 173% were reported for the optimized $\text{Yb}^{3+}/\text{Pr}^{3+}/\text{Ce}^{3+}$ tridoped $\text{CsPb}(\text{Cl}_{0.33}\text{Br}_{0.66})_3$ NCs. These codoped materials may help to minimize the importance of uncontrolled traps as intermediate states in the quantum-cutting process by instead routing energy through well-defined and well-controlled Ln^{3+} intermediate states.

The Song group has made substantial progress in integrating Yb^{3+} -doped $\text{CsPb}(\text{Cl}_{1-x}\text{Br}_x)_3$ NCs with both Si and CIGS photovoltaics.^{647,661} Impressive gains in power conversion

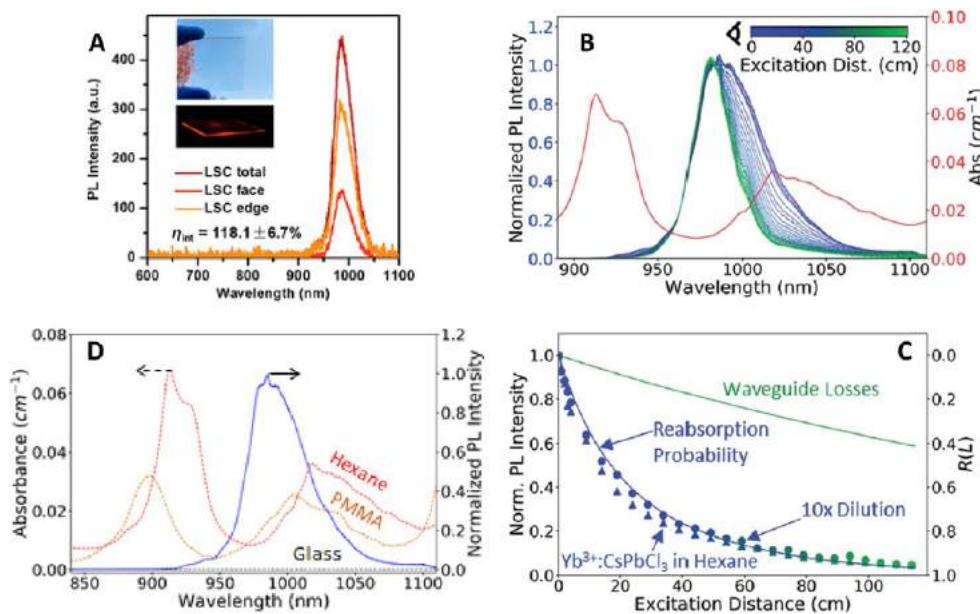


Figure 72. (A) Total (dark red), facial (light red), and edge (orange) emission spectra measured from a $5\text{ cm}^{-1} \times 5\text{ cm}^{-1}$ LSC made using Yb^{3+} -doped CsPbCl_3 NCs. The internal optical efficiency (edge-emitted photons/absorbed solar photons) of this device was measured to be $118 \pm 7\%$. The top inset shows the high transparency of the LSC to visible light, and the bottom inset shows the LSC's edge emission under UV illumination, collected with a 570 nm long-pass filter. The PLQY of these NCs was measured to be $164 \pm 7\%$ prior to incorporation into the LSC. The optical density of this LSC at the perovskite absorption edge is 0.2. (B) Normalized PL spectra of $\text{Yb}^{3+}:\text{CsPbCl}_3$ NCs suspended in hexane with o.d. ~ 0.75 at 375 nm, obtained from a liquid 1D LSC experiment at various excitation distances relative to the edge-mounted photodetector (inset). The red curve shows the absorption spectrum of the hexane solvent. (C) Integrated normalized $\text{Yb}^{3+}:\text{CsPbCl}_3$ NC PL intensity plotted as a function of excitation distance away from the photodetector for NCs in hexane with o.d. ~ 0.75 (triangles) and o.d. ~ 0.075 (circles) at 375 nm. The blue trace is the reabsorption probability predicted from a model. The green line is the experimental performance limit of the 1D LSC waveguide itself. All PL data were collected with excitation at 375 nm, and all data were collected at room temperature. (D) Absorption spectrum of hexane (red), a representative PMMA sample (orange), and Schott optical-quality glass (black) overlaid with the normalized PL spectrum of $\text{Yb}^{3+}:\text{CsPbCl}_3$ NCs (blue). Panel A is adapted from ref 655. Copyright 2018 American Chemical Society. Panels B–D are adapted with permission from ref 656. Copyright 2019 Royal Society of Chemistry.

efficiencies have been achieved simply by modifying the front surfaces of the PVs with doped perovskite NC spectral conversion layers through a solution coating method. Layer thicknesses of ~ 230 nm were found to allow the NCs to absorb most super-band-gap photons and downshift their energy *via* quantum cutting to ~ 990 nm Yb^{3+} emission, without introducing too much light scattering at sub-band-gap wavelengths that would interfere with transmission of those wavelengths to the underlying photovoltaic cell (so that lanthanide emission can be absorbed by the cell). Figure 71A shows experimental J – V data⁶⁶¹ collected for a crystalline (c) Si PV before and after coating with quantum-cutting NCs. An absolute increase of 3.1% ($>20\%$ rel.) is observed in the power-conversion efficiency of this cell. Confirmation that this increase results from spectral downshifting comes from the action spectrum of Figure 71B,⁶⁶¹ which shows little change throughout the spectral response until the perovskite band gap is reached, at which point the incident power conversion efficiency increases sharply. These results demonstrate the promise of these materials for making major improvements to photovoltaic efficiencies. The Gamelin group has performed detailed balance calculations to assess the maximum thermodynamic efficiency increases that can be anticipated from various photovoltaics types by taking advantage of this quantum cutting, using the real spectroscopic characteristics of these materials.⁶⁵⁷ Figure 71C shows the spectral characteristics of the narrowest gap $\text{Yb}^{3+}:\text{CsPb}(\text{Cl}_{1-x}\text{Br}_x)_3$ composition for which high-efficiency quantum cutting is feasible, in

comparison with the external quantum efficiency curves of multicrystalline Si, CIGS, and silicon heterojunction (SHJ) cells. SHJ technology is very nearly optimal for pairing with these quantum cutters because of its better red sensitivity. The calculations considered various known loss processes, including power saturation⁶⁵⁸ of the quantum-cutting luminescence and incomplete capture of emitted photons by the underlying cell, to project annual energy yields for different implementations. Figure 71D summarizes these calculations, showing that under all circumstances, sizable increases are anticipated. For example, a relative increase of 7.3% is anticipated in the case where the PLQY = 200%, photon capture = 75%, and the real saturation response is included. These experimental and computational results indicate that substantial progress toward exceeding the Shockley–Queisser single-junction efficiency limit can be anticipated from this technology pending engineering advances.

A second approach to harnessing the energy efficiency of these quantum-cutting NCs in solar technologies is to integrate them into LSCs. Doped NC LSCs were initially introduced using Mn^{2+} -doped ZnSe as the active material, absorbing short-wavelength solar photons and emitting from the internal Mn^{2+} d–d excited state.⁶⁷¹ This work demonstrated that doped nanocrystals excel at separating the tasks of photon absorption and photon emission, yielding the lowest reabsorption losses of any spectral downshifter investigated to date.⁶⁷² Mn^{2+} emission occurs higher in energy than desired for this technology, however, and other copper-containing luminescent NCs (e.g.,

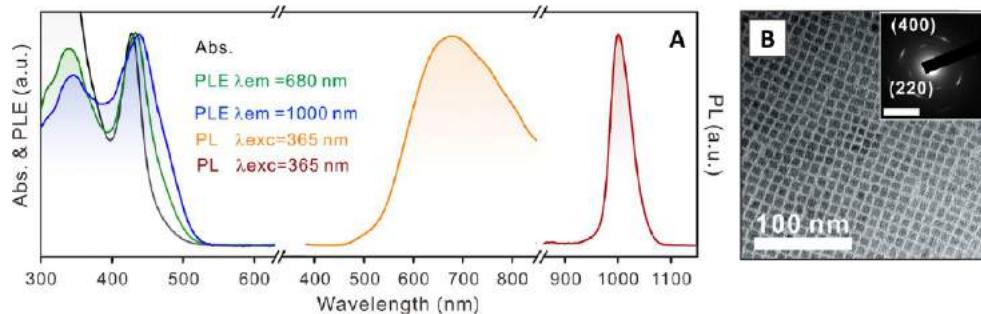


Figure 73. (A) Absorption, PL, and PLE spectra of 2.9% Yb^{3+} -doped $\text{Cs}_2\text{AgBiBr}_6$ NCs. (B) TEM image of the Yb^{3+} -doped $\text{Cs}_2\text{AgBiBr}_6$ NCs. Inset: Selected area electron diffraction pattern for the same NCs (scale bar = 2 nm^{-1}). Adapted from ref 562. Copyright 2019 American Chemical Society.

Cu^{+} -doped quantum dots or CuInS_2) have the best overall solar conversion efficiencies.^{672–676}

Two studies have investigated quantum-cutting $\text{Yb}^{3+}:\text{CsPb}(\text{Cl}_{1-x}\text{Br}_x)_3$ NCs in LSCs. The Wu group has incorporated $\text{Yb}^{3+}:\text{CsPbCl}_3$ NCs into 5 cm \times 5 cm acrylic waveguides (Figure 72A) and reported an internal optical efficiency (edge-emitted photons/absorbed solar photons) of 118% for $\text{Yb}^{3+}:\text{CsPbCl}_3$ NCs in PMMA, extrapolating to estimate the performance of large-area devices.⁶⁵⁵ The optical density of these devices was rather small (0.2 at the absorption edge), possibly because of solubility limitations within the PMMA matrix. Moreover, the band gap of $\text{Yb}^{3+}:\text{CsPbCl}_3$ NCs is large, limiting absorption to only $\sim 3\%$ of the solar flux at AM1.5. The external power conversion efficiency of the 5 cm \times 5 cm device was thus only 3.7%. Nonetheless, the power of quantum cutting and lanthanide emission is evident, resulting in high PLQYs ($\sim 164\%$ for these NCs) and very low reabsorption of the emitted light by the same lanthanide f-f transitions.

A key objective of LSCs is to concentrate photons harvested over large LSC facial areas onto small PV areas. It is therefore critical to evaluate photon losses in large-scale waveguides, for example on the scale of a building's window, because many important loss mechanisms that do not appear detrimental in short waveguides turn out to be problematic over larger distances. To this end, the Gamelin group measured waveguiding within a 120 cm 1D LSC and found that $\text{Yb}^{3+}:\text{CsPbCl}_3$ NC have negligible intrinsic attenuation losses over these very large waveguide lengths, as expected from their strongly downshifted emission and the very small extinction coefficients of the f-f transitions, but they also found severe attenuation of the f-f emission when the waveguide contained C-H bonds (high-frequency vibrations).⁶⁵⁶ This result has very important implications for any LSC work involving Yb^{3+} , because it precludes the use of popular acrylics as the waveguide medium. This group demonstrated that the problem could be reduced or removed by eliminating C-H vibrations within the waveguide medium. Implementation of this strategy in a 2D LSC will require additional waveguide innovations.

Beyond conventional 2D LSCs, Gamelin's group further proposed and modeled a "monolithic-bilayer" LSC architecture that integrates quantum-cutting NCs with conventional LSC chromophores in vertical series within the same waveguide.⁶⁵⁶ This architecture offers similar advantages of tandem LSCs, but in a much simpler configuration. Modeling predicted that a monolithic bilayer configuration could improve the performance of state-of-the-art CuInS_2 LSCs by at least 19%, for example. Instead of summing voltages from the two layers of a

tandem LSC, the bilayer device sums the currents from each layer at the same voltage, allowing use of only a single PV rather than two PVs with separate band gaps. The bilayer approach also avoids the challenge of current matching in tandem LSCs. Experimental demonstration of the device will require C-H-free waveguides, as discussed above.

In related materials, lanthanide doping of lead-free metal-halide elpasolite (so-called "double perovskite") NCs have yielded promising results that may point the way to convert these materials, which generally show strong absorption but poor luminescence, into useful luminescent materials. Three publications exploring Ln^{3+} doping of colloidal $\text{Cs}_2\text{AgInCl}_6$ NCs appeared within a few months of one another.^{562,565,568} The Kim group synthesized colloidal $\text{Cs}_2\text{AgInCl}_6$ NCs doped with Yb^{3+} , Er^{3+} , or both simultaneously, and they demonstrated that f-f emission from these lanthanides can be generated by photoexcitation of the host NCs.⁵⁶⁵ The PLQYs in these NCs were noted to be over an order of magnitude smaller than those of the $\text{Yb}^{3+}:\text{CsPb}(\text{Cl}_{1-x}\text{Br}_x)_3$ NCs, and the PLE spectra curiously did not reflect the absorption features of the materials. In parallel, the Chen group studied Yb^{3+} doping of $\text{Cs}_2\text{AgBiCl}_6$ and $\text{Cs}_2\text{AgBiBr}_6$ NCs, showing that both lattices can be used to host Yb^{3+} ions and sensitize their f-f luminescence.⁵⁶² Figure 73 summarizes some key results from this study, showing the observation of both Yb^{3+} and broad trap luminescence with UV photoexcitation of the $\text{Cs}_2\text{AgBiBr}_6$ NCs when doped with a few % Yb^{3+} . The PLE spectra track the absorption spectra, demonstrating conclusively the key result of Yb^{3+} sensitization by the $\text{Cs}_2\text{AgInCl}_6$ NC host. The Nag group also examined Yb^{3+} doping of colloidal $\text{Cs}_2\text{AgInCl}_6$ NCs.⁵⁶⁸ Their results highlighted that the sensitized Yb^{3+} PL is much stronger than the weak, broad luminescence of the undoped NCs, and that the latter gets even weaker upon introduction of Yb^{3+} . These observations show that Yb^{3+} competes with both nonradiative recombination and trapping for the energy of the absorbed photon. Although the PLQYs of all of these elpasolites were small ($< 10\%$), further synthetic advances with elpasolite NCs may help to boost this value by suppressing nonradiative decay in these materials. Notably, however, Yb^{3+} doping into $\text{Cs}_2\text{AgInCl}_6$ and other elpasolite lattices can be achieved by isovalent substitution, meaning that it occurs without formation of the same kind of closely associated charge-compensating defect hypothesized to play a role in the quantum-cutting mechanism of the $\text{Yb}^{3+}:\text{CsPb}(\text{Cl}_{1-x}\text{Br}_x)_3$ NCs. It is unclear whether such a defect level is actually necessary or merely incidental in those quantum-cutting compositions, and further development of luminescent Yb^{3+} -

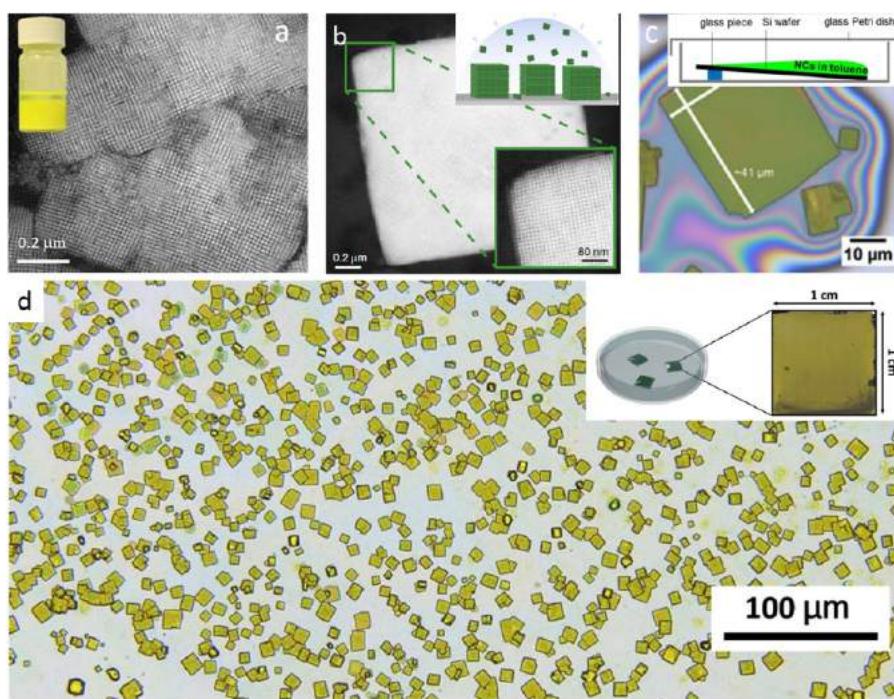


Figure 74. HAADF-STEM image of CsPbBr_3 nanocube SLs obtained by spontaneous self-assembly in solution (a) and by solvent evaporation (b). Panel a is reprinted with permission from ref 80. Copyright 2018 John Wiley & Sons, Inc. Panel b is reprinted with permission from ref 81. Copyright 2018 Nature Publishing Group. (c) Optical microscopy images of large ($50 \mu\text{m}$) CsPbBr_3 nanocube SLs prepared on top of a tilted Si wafer. Reproduced from ref 143. Copyright 2018 American Chemical Society. (d) Large-area, nearly uniform CsPbBr_3 nanocube SLs prepared on a Si substrate by solvent drying in a closed Petri dish, and the inset illustrates the experimental for self-assembly on a Si substrate in a Petri dish (left panel) and an optical microscopy image of a Si substrate (right panel) covered with densely packed SLs. Reproduced from ref 692. Copyright 2019 American Chemical Society.

doped elpasolite NCs could help to address this question. If quantum yields comparable to those found in $\text{Yb}^{3+}:\text{CsPb}-(\text{Cl}_{1-x}\text{Br}_x)_3$ NCs can ultimately be achieved in double perovskites too, their lead-free compositions would be very attractive for large-scale solar applications.

SELF-ASSEMBLY

Self-Assembly of Nanocubes. Over the last few decades, self-assembly of colloidal nano- and microparticles into long-range ordered superlattices (SLs) has been widely investigated on various material systems.^{660,677–680} Similar to atoms in crystals where the lattice defines the physical properties of the bulk compound, the NCs in the SL could eventually determine additional collective properties of the solid. This is a crucial step for the integration of the colloidal nanostructures into devices. Uniform NCs can assemble into 1D, 2D, and 3D architectures through the single component or through binary (or even ternary) self-assembly of larger and smaller particles.⁶⁷⁷ The forces that drive NC self-assembly range from hard- to soft-particle interactions. Taking advantage of previous knowledge gained on the self-assembly of conventional monodisperse colloidal NCs, a large variety of self-assembly techniques have been reported over the years such as evaporation-driven or destabilization-driven approaches, as well as spontaneous and template-assisted self-assembly.^{660,677,679} Recently, these techniques have been extended to self-assembly of halide perovskite NCs into highly ordered SLs for exploration of their collective properties that can be very different from their individual constituents.^{21,80,81,111,143,160,322,681–689} Near monodispersity of NCs and high shape uniformity are important factors to obtain long-

range ordered NC SLs.^{660,690,691} Fortunately, these conditions are easily met for all-inorganic CsPbX_3 perovskite NCs as they are often prepared with near monodispersity regardless of the synthesis method, as discussed in the synthesis section.^{14,30,53,134,143} As a result, these perovskite nanocubes tend to self-assemble into 1D or 2D SLs on a TEM grid upon solvent evaporation from a droplet of high concentrated colloidal solution. Initial examples of CsPbBr_3 nanocube SLs date back to 2017, when 2D and 3D assemblies were obtained by the solvent evaporation method.^{21,111,322} In reference 322 small superlattice domains on TEM grids exhibit a simple cubic packing of the nanocubes with a lattice constant of ≈ 12.5 nm and an interparticle separation of ≈ 2.3 nm. The SLs show a red shift of 15 nm compared to individual NCs. Upon applying high pressure, the NCs in the SLs fuse together and the corresponding SLs transform into single-crystalline nano-platelets. In refs 21 and 111 much larger 3D aggregates were obtained on silicon substrates which also exhibited a red-shifted PL peak at room temperature.

One of the interesting features of CsPbBr_3 nanocubes is that they spontaneously self-assemble into SLs in a sufficiently concentrated colloidal solution, as shown by Tong *et al.* (Figure 74a).⁸⁰ The red-shifted PL from SLs makes them better suited as pure-green emitters (ideal wavelength of ~ 530 nm), whereas individual nanocubes emit below 518 nm. In ref 80 the origin of the red shift was attributed to the mini-band formation caused by the electronic coupling of nanocube subunits in SLs. Interestingly, the colloidal SLs partially preserve their supercrystal morphology even after halide exchange reaction, and thus their optical properties are easily tunable across the visible wavelength range. However,

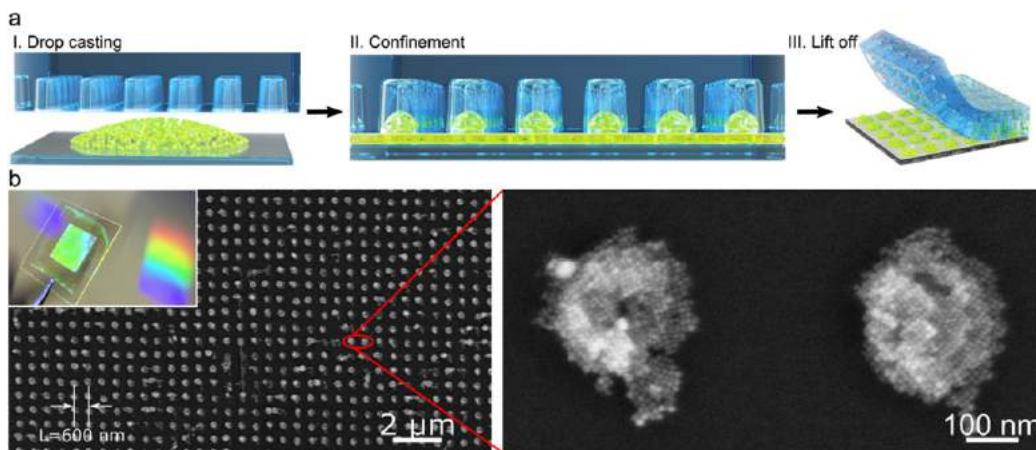


Figure 75. (a) Schematic illustration of PDMS template assisted self-assembly CsPbBr_3 nanocubes into 2D photonic SLs. (b) Corresponding SEM images of 2D photonic CsPbBr_3 SLs with lattice parameters of 600 nm (inset: photograph of the CsPbBr_3 SL arrays on glass substrates under white light illumination). Reproduced with permission under a Creative Commons CC-BY License from ref 688. Copyright 2020 John Wiley & Sons, Inc.

spontaneous self-assembly comes with less control over the morphology and size of the produced SLs. On the other hand, solvent drying techniques produce large area well-defined square-shaped 3D CsPbBr_3 SLs, as initially demonstrated by Kovalenko *et al.* (Figure 74b).^{81,111} Interestingly, these SLs generate short, intense bursts of light so-called superfluorescence - upon light excitation due to coherent and cooperative emission of nanocubes in the SLs.⁸¹ The peak position of superfluorescence red-shifted with more than 20-fold accelerated radiative decay as compared to uncoupled nanocubes. Recently, a similar phenomenon has been reported in CsPbBr_3 SLs by Xie and co-workers.⁶⁹³ They claimed that the stimulated emission of nanocube assemblies in SLs is not limited by the traditional population-inversion condition. However, the SLs reported in that work are not well-defined regarding their morphology and the yield appears to be low based on the given electron microscopy images.

Several attempts have been made to optimize the solvent drying technique to achieve large area cubic SLs with high yield.⁹⁴³ One of the critical factors for obtaining SLs is the size distribution and shape purity of the corresponding perovskite NC building blocks. In this regard, Imran and co-workers¹⁴³ showed the fabrication of large cubic or rectangular 3D SLs ($\sim 50 \mu\text{m}$ lateral size) in very high yield using the shape-pure and nearly monodisperse CsPbBr_3 nanocubes prepared using secondary aliphatic amines (Figure 74c). Such large size SLs have been accomplished by evaporation of solvent from a colloidal solution on top of a tilted Si wafer either inside a glovebox or at ambient conditions (inset of Figure 74c). Furthermore, large area, nearly uniform CsPbBr_3 NC SLs were prepared by slow solvent evaporation on a Si substrate placed in a closed petri dish (Figure 74d), and the structural coherences of these SLs were revealed by SL reflection peaks in wide-angle X-ray diffraction measurements.⁶⁹² These are fingerprint peaks to long-range order and high crystallinity of nanocubes and the angular separation if these peaks are very sensitive to the periodicity of SL. It is very important to consider that the NCs of SLs can coalesce into larger structures, and this can significantly affect their PL properties by energy-transfer process.⁸³ Despite significant progress toward the fabrication of high-quality CsPbBr_3 nanocube 3D SLs, only a few studies have been published on the preparation

of 2D and 1D SLs.^{681,683,694} Very recently, Patra *et al.* demonstrated the preparation of ultrasmooth self-assembled monolayers using CsPbBr_3 nanocubes functionalized with short-chain thiocyanate ligands (SCN^-).⁶⁸³

Device applications of SLs will most likely require control over their dimensionality and positioning on a given solid substrate. However, it is extremely difficult to fulfill these conditions using the self-assembly techniques discussed above. Alternatively, template-assisted self-assembly has been gaining significant attention to achieve these conditions.^{685,695,696} However, the packing of perovskite NCs in the assemblies patterned by this approach has yet to be investigated in detail. Very recently, David *et al.*⁶⁸⁸ reported the fabrication of 2D perovskite photonic SLs using prepatterned PDMS templates. The height and lateral dimensions of the SLs were controllable by the predesigned PDMS template (Figure 75a,b). These photonic crystals exhibit field enhancement at NIR excitation by a light trapping mechanism. However, such self-assemblies are not perfect as the SLs obtained by the slow solvent evaporation approach (Figure 75b). Therefore, there is still plenty of room for the optimization of perovskite SLs obtained by the template-assisted assembly. Despite rapid developments in the field of perovskite NCs, there is still a lack of knowledge on the various NC assemblies such as free-standing SLs, binary and ternary SLs.

Self-Assembly of Anisotropic LHP NCs. Self-assembly of other shapes including nanorods,⁶⁸⁶ nanowires,^{22,697} and nanoplatelets⁶⁸² has also been reported. For instance, Yang and co-workers⁶⁸² reported the self-assembly of 2D perovskite nanosheets by a layer-by-layer approach. Interestingly, the 2D perovskite nanosheets SLs resemble Ruddlesden–Popper layered perovskite phase. This self-assembly process is reversible as the SLs transform into individual building blocks upon sonication. One-dimensional (1D) NWs show potential anisotropic optoelectronic properties when they are highly oriented. It has been shown that oriented self-assemblies of perovskite NWs were obtained at the air-liquid interface by Langmuir–Blodgett technique.^{22,697} However, the ionic nature of halide perovskites limits their stability at air-water assembly interface. To realize the assembly of perovskite NWs with better stability against water, a core–shell-type configuration has been introduced using the amphiphilic block copolymer

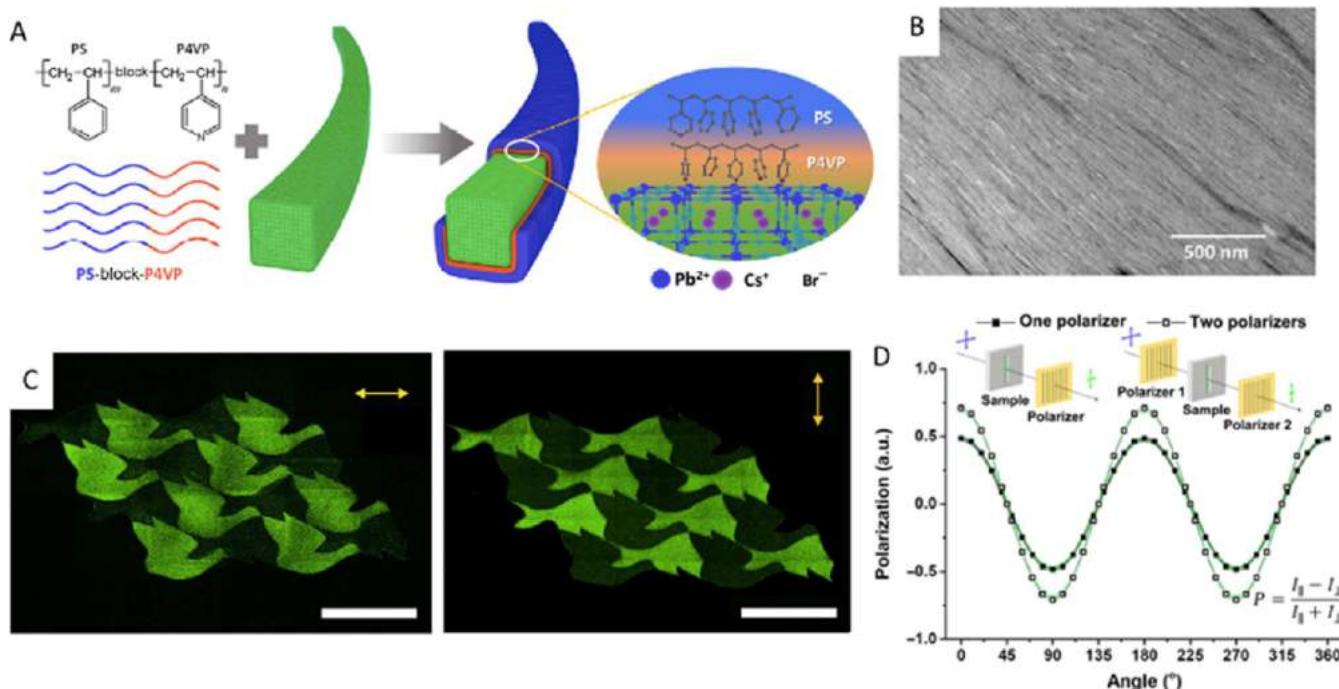


Figure 76. (A) Schematic illustration of synthesis of block-copolymer-coated CsPbBr₃ NWs with core–shell configurations. (B) Self-assembled NW monolayer using the Langmuir–Blodgett method. Reproduced with permission from ref 697. Copyright 2020 Springer Nature. (C) Polarized emission from printed polymer–CsPbBr₃ NW composite with horizontal polarization (left) and vertical polarization (right). Scale bars, 1 mm. (D) Polarized emission from printed perovskite NW composites as a function of different angles. Reproduced with permission under a Creative Commons CC BY-NC license from ref 699. Copyright 2019 The Authors.

such as polystyrene-block-poly(4-vinylpyridine) (PS-P4VP) (Figure 76A,B).⁶⁹⁷ The shelling polymer materials can not only prevent the NW bundling, ensuring a better solution dispersion, but also improve the stability of NWs against water, due to the blocking effect of hydrophobic polystyrene. For perovskite NWs, the PLQY typically shows significant reduction due to their large surface to volume ratio comparing with NCs, the polymer coating represents an effective strategy for the enhancement of their absolute quantum efficiency due to the passivation effect. With a modified Langmuir–Blodgett technique, the polymer-coated perovskite NWs were able to assemble into a uniform monolayer with the uniaxial alignment at the air-liquid interface. The anisotropic polarized PL emission was detected at different angles from the oriented nanowire monolayers.

In addition to the conventional patterning method, a direct ink writing technique has been developed using the aligned cellulose fibrils embedded into a hydrogel matrix.⁶⁹⁸ This method can control the anisotropic alignment of nanocomposite with 3D architectures. The polymer-coated perovskite NW bundles were used as a printing nanocomposite ink.⁶⁹⁹ It is possible to control the orientation of polymer-perovskite NW nanocomposites through the 3D printing technique, which influences their polarized PL emission (Figure 76C,D). The polarization anisotropy in 3D-printed perovskite NW composite could be promising for optical device applications.

MORPHOLOGICAL AND STRUCTURAL CHARACTERIZATION

As discussed in previous sections, the morphology and crystal structure of perovskite NCs play an important role in their optical properties. This section is focused on the morpho-

logical and structural characterization of perovskite NCs using electron microscopy and X-ray scattering techniques, respectively. LHPs are very sensitive to electron beam illumination and they often tend to degrade into metallic Pb. In particular, it is extremely difficult to obtain high-resolution electron microscopy images. Therefore, electron microscopy images of perovskite NCs have to be acquired with extreme care. We discuss the current challenges and recent advances in electron microscopy studies on various kinds of perovskite NCs. On the other hand, various X-ray scattering techniques have been used for the structural characterization of perovskite NCs and their assemblies. We discuss the application of various X-ray scattering techniques on PeNCs, ranging from common XRD measurements to advanced synchrotron-based *in situ* measurements with 2D detectors. In particular, studies about phase-stability and degradation are discussed. In addition, we discuss X-ray scattering studies used to investigate structure–function correlations.

Electron Microscopy. Aberration-corrected (scanning) transmission electron microscopy ((S)TEM) has become a standard technique to investigate nanomaterials at the atomic level. With the development of C_s (spherical aberration) and C_c (chromatic aberration) corrected microscopes, it has become feasible to obtain structural information at the atomic scale, even using low acceleration voltages. Such investigations allow us to correlate the (atomic) structure of nanomaterials with their chemical and physical properties. The acquisition of atomically resolved (S)TEM images of halide perovskites using conventional electron dose rates is however hindered by their sensitivity to the energetic electron beam. Upon illumination, structural damage and/or phase transitions could occur, which hampers a visualization/characterization of the initial (crystal) structure of the halide perovskite NCs. Therefore, electron

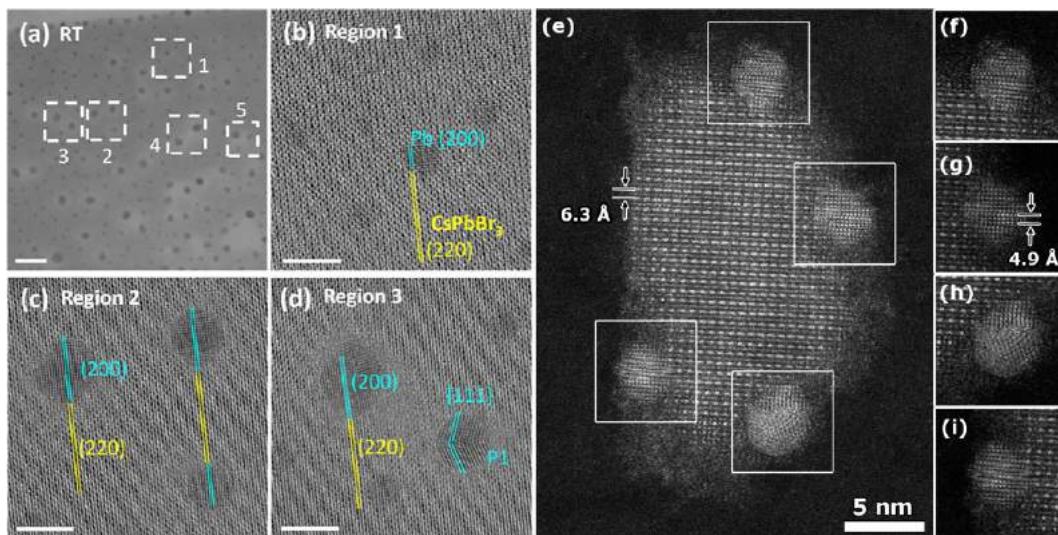


Figure 77. (a–d) High-resolution TEM analysis of the formation of metallic Pb particles on a 3 nm thick CsPbBr₃ nanosheet at room temperature: (a) overview image (scale bar: 20 nm) and (b–d) high-resolution TEM images of three regions of interest in (a), which show the presence of Pb particles (scale bars: 5 nm). Reproduced from ref 139. Copyright 2017 American Chemical Society. (e–i) High-resolution HAADF-STEM image of a CsPbI₃ NC showing the presence of bright spherical particles mainly at the edge of the nanoparticle (f–i). These particles were identified as metallic Pb. Reproduced with permission from ref 30. Copyright 2016 John Wiley & Sons, Inc.

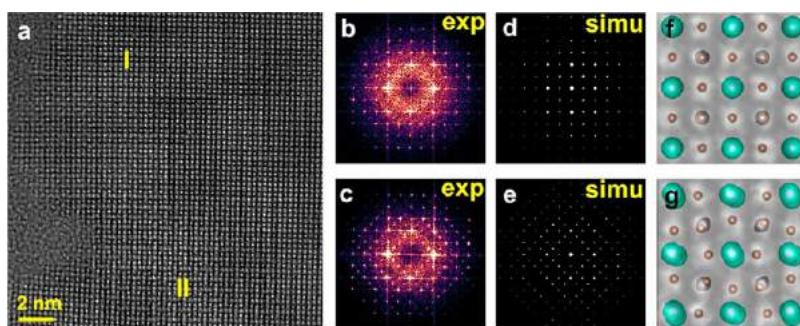


Figure 78. Aberration-corrected high-resolution TEM performed on CsPbBr₃ showing the coexistence of the cubic and the orthorhombic phases. (b,c) Fourier transforms from regions I (b) and II (c), which are highlighted in image (a). (d,e) Simulated electron diffraction patterns of the cubic (d) and the orthorhombic (e) CsPbBr₃ phase. (f,g) Enlarged images from regions I (f) and II (g). The cubic and orthorhombic structure models are overlaid on (f) and (g), respectively. Reproduced from ref 702. Copyright 2016 American Chemical Society.

microscopy studies of halide perovskite NCs have to be performed with extreme care.

Degradation of LHP NCs under the Electron Beam. Illuminating halide perovskite NCs with an energetic electron beam results in the rapid formation of high contrast particles, hampering the acquisition of an image at both nano and atomic scale of halide perovskite NCs. Such behavior has been reported in multiple studies using either a parallel beam in TEM mode (Figure 77a–d) or a focused electron probe in STEM mode (Figure 77e–i).^{16,30,48,74,139,700,701} Yu *et al.* performed comparative studies on lead-halide perovskite nanostructures at both low and high accelerating voltages in both TEM and STEM mode, which showed clear, rapid formation of high contrast particles in all cases.⁷⁰² Different claims have been made about the nature of these nanometer-sized nanoparticles and the resulting structural deformations in the perovskite NC.^{16,30,48,702} Recently, Dang *et al.* demonstrated that these particles consist of metallic lead and that their nucleation mainly results from a radiolysis process.¹³⁹ It was shown that at both low and high irradiation voltages desorption of halogen atoms from the surface of the perovskites and reduction of

Pb²⁺ ions to Pb⁰ were induced by the interaction with the electron beam. Subsequently, neighboring Pb⁰ atoms diffused and aggregated into nanometer-sized, spherical Pb particles. The formation of such metallic lead nanoparticles preferentially occurs at the edges and corners of the perovskite NCs. Halide perovskite NCs with a high surface area to volume ratio, such as thin nanowires and nanoplatelets, are therefore more susceptible to such electron beam induced damage.¹³⁹ Next to the formation of metallic lead particles, degradation and loss of crystallinity at the edges and/or corners of halide perovskite NCs are additional challenges when investigating (thin) halide perovskite NCs. Both phenomena can be observed in movie S2 (degradation of a CsPbBr₃ nanocube upon continuous scanning of the electron beam) and Figure S1 (a few selected high-resolution HAADF-STEM frames of movie S2), where the degradation of a single CsPbBr₃ nanocube is observed. This complicates the investigation of the surface termination of halide perovskite NCs since such degradation is (extremely) rapid depending on the thickness of the nanomaterial.

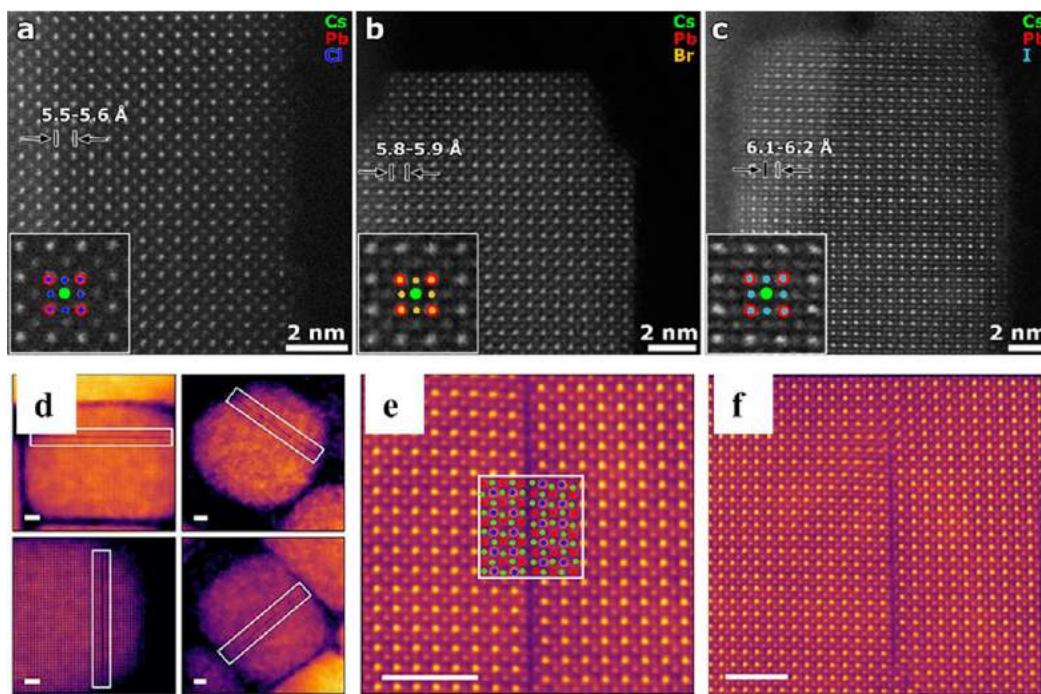


Figure 79. High-resolution HAADF-STEM images of (a) CsPbCl_3 , (b) CsPbBr_3 , and (c) CsPbI_3 perovskite nanowire. The different atomic columns are identified using the intensity–atomic number relation in HAADF-STEM imaging. Reproduced with permission from ref 22. Copyright 2016 John Wiley & Sons, Inc. (d) Overview HAADF-STEM images showing the presence of Ruddlesden–Popper planar defects (highlighted as rectangular boxes) in several CsPbBr_3 NCs. (e) Atomic-resolution HAADF-STEM image of a Ruddlesden–Popper planar defect with an overlaid atomic model (blue, Pb; red, Cs; green, Br). (f) Atomic-resolution HAADF-STEM image of a Ruddlesden–Popper planar defect extending only a few unit cells. The scale bars correspond to 3 nm. Reproduced from ref 707. Copyright 2018 American Chemical Society.

Acquisition of Atomically Resolved Images. All-Inorganic Halide Perovskite NCs. To overcome electron beam-induced sample degradation, aberration-corrected high resolution TEM,^{703–705} low-dose in-line holography,⁷⁰² and dose-controlled aberration-corrected STEM imaging^{22,30,73,702,706,707} have been successfully applied to study all-inorganic lead-halide perovskite nanomaterials at the atomic level. Yu *et al.* initially visualized the pristine structure of ultrathin two-dimensional CsPbBr_3 perovskites by applying low-dose in-line holography.⁷⁰² Using this low-dose technique, a series of aberration-corrected high-resolution TEM images were acquired and the phase information was extracted by reconstructing the image series. The atomic structure of these two-dimensional CsPbBr_3 perovskites was successfully studied before any electron beam-induced sample alterations had occurred. This study revealed the coexistence of the high-temperature cubic and the low-temperature orthorhombic phases in such CsPbBr_3 nanosheets. It must be pointed out that the two phases have a close structural similarity, where only a small tilting of the PbBr_6 octahedra is necessary to transform from the cubic phase into the orthorhombic phase. To distinguish between these two phases, high-quality data with an optimal resolution are required. In addition, they also successfully acquired single dose-controlled aberration-corrected high resolution TEM images using a negative C_s which revealed this two-phase coexistence (Figure 78a). The spatial resolution in these images is sufficient to directly observe the octahedral tilting in the experimental images in Figure 78fg; however, the difference is more clearly observable in the Fourier transforms in Figure 78b,c.

Multiple aberration-corrected high resolution HAADF-STEM studies have been carried out to investigate the crystal structure of all-inorganic lead-halide perovskite NCs.^{22,30,73,702,706,707} The advantage of STEM imaging in comparison to TEM imaging is that the intensity in such an image scales with the projected thickness of the NC and the average atomic number of the elements present along the projection direction. This intensity–atomic number relation can be exploited to identify atomic columns based on their composition if a significant atomic number difference is present for the different elements. Thereby, the use of high resolution HAADF-STEM imaging will enable a direct identification of the different atomic columns in the perovskite NC under investigation (at a location of similar thickness), which is an advantage of using STEM in comparison to TEM. For example, for CsPbBr_3 perovskites with $Z_{\text{Pb}} = 82$, $Z_{\text{Cs}} = 55$, and $Z_{\text{Br}} = 35$ (Figure 79b), this relation can be exploited to distinguish the different atomic columns in the cubic [100] or orthorhombic [110] zone in a straightforward manner. In this orientation, the bright atomic columns in the cubic [100] or orthorhombic [110] zone are mixed Pb–I columns with an average atomic number of 58.5 due to the alternating nature of the presence of Pb and I atoms in the column, which have higher atomic numbers than Cs and Br. Subsequently, the Cs atomic columns will appear brighter than the Br columns since Cs is heavier than Br, which have the lowest intensity value. This intensity–atomic number relation (in combination with the knowledge on the crystal structure) will also enable the elemental identification of CsPbCl_3 and CsPbI_3 perovskites (Figure 79a,c, respectively). This powerful technique has been used to study various all-inorganic halide perovskites. For

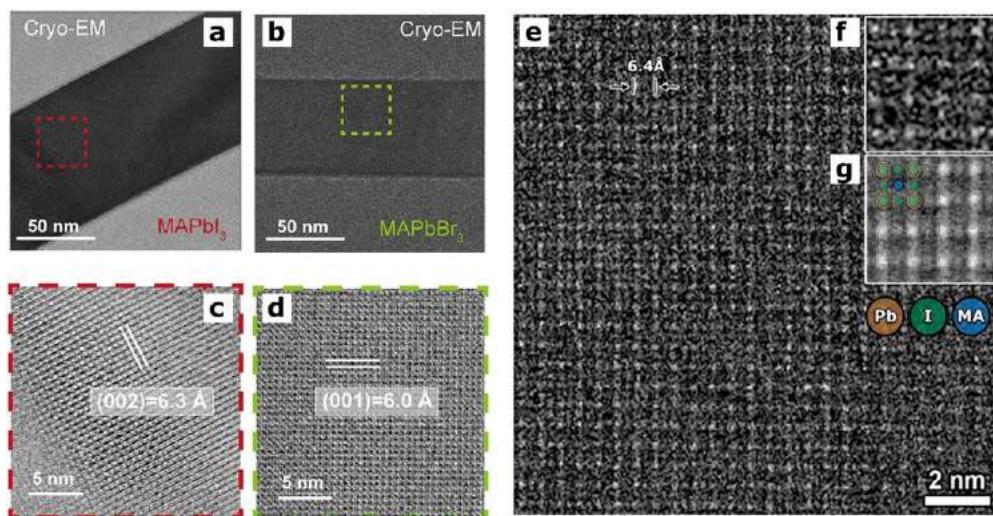


Figure 80. (a–d) Cryo-EM investigation of $\text{CH}_3\text{NH}_3\text{PbI}_3$ and $\text{CH}_3\text{NH}_3\text{PbBr}_3$ nanowires. Overview cryo-EM images of both rods are visualized in (a) and (b). Atomically resolved TEM images capturing both the PbI_6 octahedra and the methylammonium molecules in $\text{CH}_3\text{NH}_3\text{PbI}_3$ (c) and $\text{CH}_3\text{NH}_3\text{PbBr}_3$ (d). Panels a–d are reproduced with permission from ref 710. Copyright 2019 Elsevier. (e–g) Low-dose aberration-corrected HAADF-STEM imaging in combination with a template-matching procedure on a $\text{CH}_3\text{NH}_3\text{PbI}_3$ NC. The atomic arrangement of the $\text{CH}_3\text{NH}_3\text{PbI}_3$ NC is clearly resolved in the averaged template (g) of the low-dose HAADF-STEM image in (e), performed on the template image in (f). Reproduced with permission under a Creative Commons CC-BY-NC from ref 273. Copyright 2017 The Authors.

example, Tong *et al.* revealed that CsPbBr_3 nanowires were formed through oriented-attachment mechanism of initially formed CsPbBr_3 nanocubes by imaging an intermediate nanowires.²² Morrell *et al.* visualized the presence of Ruddlesden–Popper planar defects in CsPbBr_3 NCs at the atomic level (Figure 79d–f).⁷⁰⁷

Organic–Inorganic Hybrid Halide Perovskite NCs. The characterization of organic–inorganic hybrid halide perovskite NCs is even more challenging since these perovskites tend to degrade instantaneous upon electron beam illumination.^{16,700} Recently, a few successful studies on methylammonium-based hybrid perovskites have been performed using low-dose high resolution TEM,³⁰ cryogenic electron microscopy (cryo-EM),³⁶⁷ low-dose aberration-corrected HAADF-STEM²⁷³ and integrated differential phase contrast STEM (iDPC-STEM).⁷⁰⁸ The initial atomically resolved HRTEM image of a $\text{CH}_3\text{NH}_3\text{PbBr}_3$ perovskite was collected using a Gatan K2 direct-detection electron-counting camera by Zhang *et al.*⁷⁰⁹ The high detective quantum efficiency of a direct-detection camera enables the investigation of highly beam sensitive materials as extremely low-dose conditions can be applied. In this work, they revealed that the $\text{CH}_3\text{NH}_3\text{PbBr}_3$ crystals consist of ordered nanometer-sized domains with off-centered CH_3NH_3 cations with an in-plane and out-plane orientation, which provides direct evidence of the ferroelectric order in $\text{CH}_3\text{NH}_3\text{PbBr}_3$. Cryo-EM is a technique which is often used to study the native state of a material/specimen by rapidly freezing the material. This technique is mostly used in life sciences. Recently, Li *et al.* preserved the native state of methylammonium-based hybrid perovskites by plunge-freezing the sample in liquid nitrogen which enabled them to observe the atomic structure of the native state of $\text{CH}_3\text{NH}_3\text{PbI}_3$ and $\text{CH}_3\text{NH}_3\text{PbBr}_3$ nanowires (Figure 80a–d).⁷¹⁰ The high resolution cryo-TEM images were acquired at a temperature of $-175\text{ }^\circ\text{C}$ using a direct detection camera in electron counting mode. The use of such cameras will be of key importance to further progress in the study of these beam

sensitive hybrid halide perovskites. In addition to these low-dose HRTEM studies, the use of HAADF-STEM has also been proven successful for the study of hybrid halide perovskites although it is often considered to be more destructive when imaging halide perovskites. Debroye *et al.* were able to retrieve the native atomic structure of $\text{CH}_3\text{NH}_3\text{PbI}_3$ NCs using low-dose aberration-corrected HAADF-STEM imaging in combination with a template-matching procedure (Figure 80e–g).²⁷³ The low-dose condition resulted in the acquisition of a single HAADF-STEM image (Figure 80e) with a very low signal to noise ratio hampering the interpretability of the image. The template matching algorithm statistically averaged a small part of the HAADF-STEM image resulting in an image with an improved signal to noise ratio. Such an algorithm searches throughout the image for specific regions which match the template (Figure 80f). In this work, the perovskite lattice of a hybrid lead iodide perovskite was successfully observed in the final averaged template in Figure 80g. This technique can only be used for an averaged observation of the crystal structure, local defects, and/or the surface termination of the NC cannot be investigated using this averaging technique. The development of pixelated electron detectors has enabled another approach for low-dose high resolution STEM imaging using iDPC-STEM. A early iDPC-STEM attempt for the investigation of $\text{CH}_3\text{NH}_3\text{PbBr}_3$ perovskites was performed by Song *et al.*⁷⁰⁸

Going beyond Qualitative Images. Quantitative methods are emerging to retrieve additional in-depth information on halide perovskite NCs such as the measurement of lattice parameters unit cell by unit cell. Such a measurement will enable the unambiguous identification of the cubic and orthorhombic structure of lead-halide perovskite NCs, which differ approximately 0.05 \AA in lattice parameter. This requires the identification of the different atom types and a precise measurement of their atomic column positions. In addition, the precise localization of the atom positions enables the investigation of possible PbX_6 ($\text{X} = \text{Cl}, \text{Br}, \text{I}$) octahedral tilt,

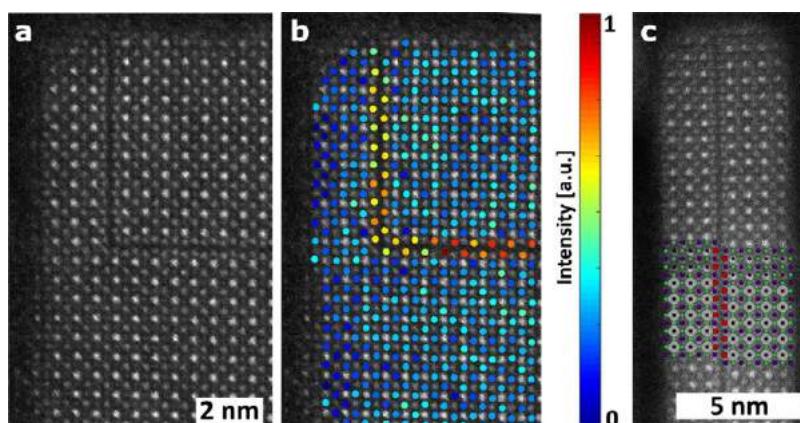


Figure 81. (a) High-resolution HAADF-STEM image of a $\text{CsPb}(\text{Cl:Br:I})_3$ NC showing the presence of plane shifts. (b) Calculated volume of the fitted Gaussian peaks of the halide columns of the NC indicates increased intensity values of the halide columns around the Ruddlesden–Popper planes, confirming an increased concentration of iodide ions at these positions. (c) Ruddlesden–Popper plane shift model (Cs^+ = purple, Pb_2^+ = black, Cl^-/Br^- = blue, I^- = red, and PbX_6 octahedra = gray) overlapping an HAADF-STEM image of a $\text{CsPb}(\text{Cl:Br:I})_3$ NC. Reproduced under a Creative Commons CC-BY-NC-ND license from ref 713. Copyright 2019 American Chemical Society.

which is expected in the orthorhombic phase. In principle, such an analysis can be performed both using aberration-corrected TEM and STEM imaging. However, the identification of the atom types in each atom column in atomically resolved TEM images is not straightforward, since the intensity in such images is not sensitive to chemical information. In order to distinct between different atom types, a quantitative statistical phase analysis needs to be carried out. In this manner, tilting of the PbX_6 octahedron was observed in CsPbBr_3 nanosheets using in-line holography (Figure 80f,g).⁷⁰² In addition, a unit cell by unit cell characterization of the lattice parameters showed that both the cubic and orthorhombic phases exhibit a lattice expansion compared to their bulk counterpart, while still being able to identify orthorhombic regions from cubic regions as they exhibit smaller lattice distances.⁷⁰² Quantification of the atom positions in an atomically resolved STEM image of a CsPbX_3 ($\text{X} = \text{Cl}, \text{Br}, \text{I}$) NC can be performed in a more straightforward manner, since the average atomic numbers of the different atom columns are sufficiently large and the intensity in such images scales with the atomic numbers of the present elements. Van der Stam *et al.* confirmed a lattice contraction after a cation exchange in colloidal CsPbBr_3 NCs resulting in doped $\text{CsPb}_{1-x}\text{M}_x\text{Br}_3$ NCs ($\text{M} = \text{Sn}^{2+}, \text{Cd}^{2+}$, and Zn^{2+} ; $0 < x \leq 0.1$).³⁰⁴ Here, the lattice parameters are quantified using statistical parameter estimation theory^{711,712} to retrieve the atom positions of each atom column. In addition, the intensity–atomic number relation in HAADF-STEM imaging can be used to identify different atom types in mixed-halide perovskites. Akkerman *et al.* investigated all-inorganic Ruddlesden–Popper double Cl–I and triple Cl–Br–I lead-halide perovskite NCs and the position of the different halides in the perovskite structure using quantitative high resolution HAADF-STEM imaging (Figure 81).⁷¹³ The intensities of the halide atom columns were calculated by fitting a Gaussian function to each atom column (Figure 81b). This work revealed that the small amount of iodide clusters at the Ruddlesden–Popper planes. Until now, quantitative (S)TEM techniques have only been applied successfully to all-inorganic halide perovskite NCs.

Summary and Outlook for Electron Microscopy Studies on MHP NCs. The previous sections have shown that halide

perovskites have been studied successfully at the atomic level using a range of techniques. Although these perovskites are very sensitive to the electron beam, the use of a parallel beam as a focused probe has been exploited. Most of these studies dealt with beam damage and therefore often low-dose conditions are required to study the native state of these halide perovskites. Recently, a few successful studies have been performed on organic–inorganic hybrid halide perovskite NCs. The use of detectors with a high detective quantum efficiency has played a big role in lowering the necessary dose needed to study the native state of hybrid halide perovskites. Despite recent advances, there are still many challenges in electron microscopy of perovskite NCs. For example, quantitative determination and location of dopants in perovskite NCs is one of the main challenges to be addressed for a better understanding of doped-perovskite NCs. It is well-known that LHPs undergo phase changes at certain temperatures, and this has often been studied by optical and X-ray characterization. It would be very interesting to probe such phase changes at the atomic level with *in situ* electron microscopy characterization at the single-particle level to obtain additional insights. Another important challenge is to apply 3D atomic imaging techniques to perovskite NCs to study their crystal structures.

X-ray Scattering Techniques and Their Impact on the Stability and Degradation Analysis of Perovskite NCs.

X-ray scattering is a powerful technique to investigate structures not only on atomic lengths scales (angstroms, Å) but also on the mesoscale (nanometer). High time resolution is feasible, especially with synchrotron radiation, and *in situ* investigations on many different NC systems are conceivable. This approach gives insights into the kinetics as well as structure–function correlations. In particular, when coupled to other *in situ* techniques, *e.g.*, UV/vis or photoluminescence measurements, X-ray scattering is a versatile and fruitful technique for providing a quantitative understanding.

So far, X-ray scattering techniques have shown a high impact by analyzing the crystal structure of perovskite NCs: in addition to probing the inherent crystal structure (crystal lattice topography), the ordering and alignment of perovskite NCs (superstructure) can be analyzed. Thus, X-ray scattering

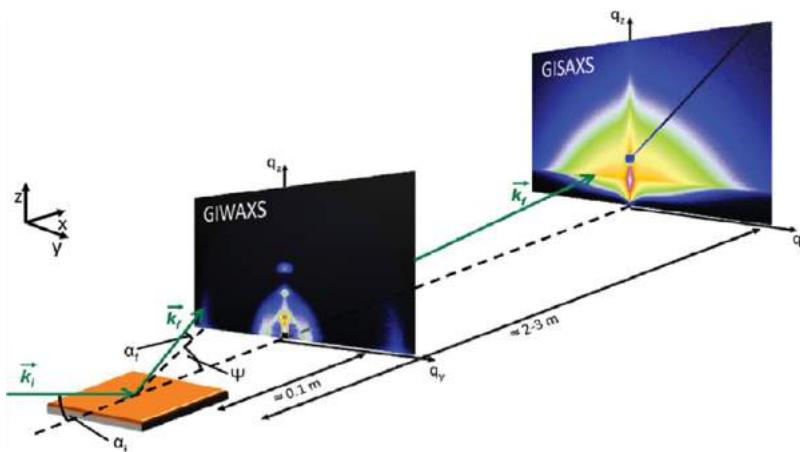


Figure 82. Schematic illustration of a typical GIXS setup with reference geometry. Photons with wavevector \vec{k}_i impinge on the sample under an incidence angle α_i . Scattered photons with wavevector \vec{k}_f leave the sample under an in-plane exit angle α_f and an out-of-plane exit angle Ψ . GIWAXS and GISAXS require different sample–detector distances, typically in the range of around 100 mm and 2–3 m, respectively. Reproduced with permission from ref 725. Copyright 2019 John Wiley & Sons, Inc.

techniques are a precise analysis tool for crystal and superstructure, crystal orientation, phase identification and phase change tracking in perovskite NCs, which are used in different areas ranging from photovoltaic and photodetectors to LEDs.^{223,334,714–716}

The focus of this section lies in the application of various X-ray scattering techniques on perovskite NCs, ranging from common XRD measurements to advanced synchrotron-based *in situ* measurements with 2D detectors. In particular, studies about stability and degradation will be mentioned, as well as studies about structure–function correlations. We aim to give also insights into more advanced scattering techniques such as grazing-incidence small- and wide-angle X-ray scattering (GISAXS and GIWAXS) and experimental setups that will help to improve perovskite NC research and facilitate the road toward broader use of mentioned methods.

Fundamental understanding of the stability of perovskites is still one of the big challenges in the field.^{85,110,717} Thus, mechanisms of degradation have to be investigated in detail and, whenever possible, with high time resolution. Investigations that capture processes in real time are commonly referred to as *in situ* (in place) in contrast to *ex situ* (out of place) experiments, that only capture the status after the time-dependent process. *In situ* experiments usually pose additional experimental challenges, *e.g.*, the necessity of high flux X-ray radiation (*e.g.*, *via* synchrotron access) and transportable experimental setups, detailed knowledge of reaction kinetics, as well as considering damage induced by the high-intensity X-ray beam. *In situ* and *operando* studies have already been used heavily on bulk and thin-film materials and offer many possibilities in perovskite NC thin-film analysis including the elucidation of superstructural features.^{718–722}

Introduction to X-ray Scattering Methods Used in the Characterization of MHP NCs. Elastic X-ray scattering is a nondestructive reciprocal space technique, *i.e.*, it yields the Fourier transform of the electron density of the probed material. This results in a diffraction pattern that contains information about typical reciprocal distances in the sample, denoted \vec{G} . These distances can be probed by X-ray scattering. Photons of wavelength λ impinge on the sample and are scattered if they fulfill the Laue condition

$\vec{k}_f - \vec{k}_i = \vec{\Delta k} = \vec{G}$, with incoming wavevector \vec{k}_i , final wave vector \vec{k}_f and reciprocal lattice vector \vec{G} . Thus, the momentum change of the photon depends on the structural lattice ordering of the sample. The momentum change q can be converted to a real space distance d using the equation $q = 2\pi/d$. The scattering event results in a change in the photon's trajectory which can be given as an angle 2θ using the Bragg equation $n\lambda = 2d \sin \theta$. Diffraction peaks (reflexes) are indexed according to the diffractive planes that give rise to the interference pattern. For indexing, Miller indices (hkl) are used. Further details about diffraction techniques on functional material, *e.g.*, perovskite LED and PV application, can be found in literature.^{677,723,724}

In laboratories, XRD in Bragg–Brentano reflection geometry is well-suited for thin-film studies including perovskite NCs. In addition to classical XRD measurements, with the use of 2D detectors, additional scattering methods have been established. Depending on the detector placement, small- or wide-angle X-ray scattering (SAXS or WAXS) can be observed, which corresponds to large and small distances probed, respectively. Whereas SAXS and WAXS are very powerful for the analysis of volume samples, to study supported thin films can be challenging. A substantial contribution from the support material can challenge the analysis of the thin film. In such cases, grazing-incidence small- and wide-angle X-ray scattering offer possibilities for structure analysis. GISAXS and GIWAXS are performed in reflection geometry with a fixed grazing-incidence angle ($\alpha_i \ll 1^\circ$). This offers the possibility to minimize substrate contributions to the scattering signal by selecting an incidence angle below the critical angle of the substrate, thus preventing the penetration of the incident beam into the substrate and/or subsequent layers. X-ray scattering is not a local method like high-resolution real-space imaging and can probe an ensemble of small crystallites, with the probe volume depending on the beam size. In particular, when considering the grazing-incidence geometry, the illuminated surface area can be rather large (order of mm^2). The probed volume depends on the penetration depth, which is dependent on the X-ray wavelength and the sample material.

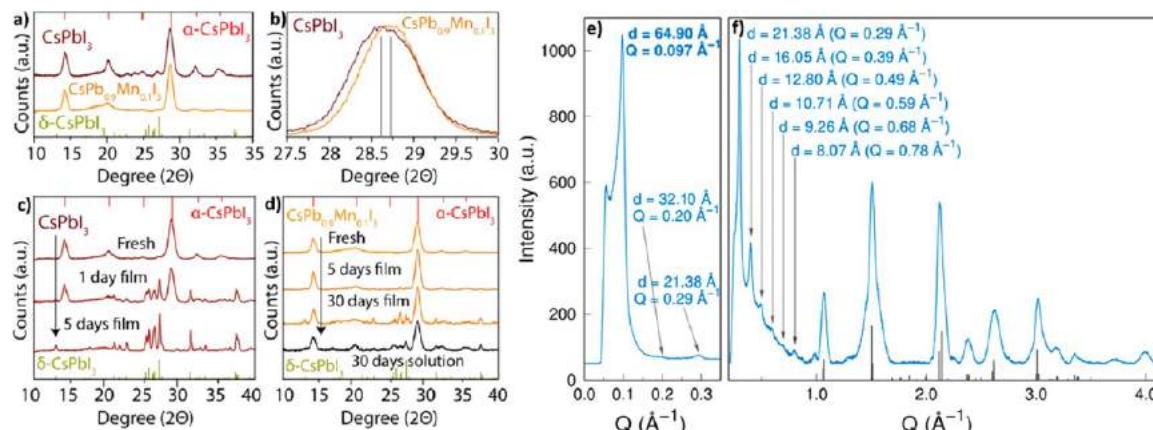


Figure 83. (a) XRD patterns of CsPbI_3 and Mn^{2+} -substituted phase. The calculated α - and δ -phase patterns are shown in red and green, respectively. (b) Zoom in of (a) to visualize the shift in Bragg peak position due to Mn^{2+} -induced lattice parameter changes. (c,d) Time-dependent XRD patterns of CsPbI_3 and $\text{CsPb}_{0.9}\text{Mn}_{0.1}\text{I}_3$ over several days, showing the difference in degradation kinetics. Reproduced from ref 607. Copyright 2017 American Chemical Society. (e,f) Low- and high-angle XRD pattern of CsPbBr_3 nanoplatelets. The first peak corresponds to a distance of the NPs of 6.5 nm. Higher harmonics are also visible, which confirms the high degree of long-range order. The NPs have a thickness of around 3.5 nm, as confirmed by TEM imaging. From the high-angle region, an orthorhombic structure could be determined. Reproduced from ref 210. Copyright 2019 American Chemical Society.

A typical experimental GIXS setup is shown in Figure 82.⁷²⁵ The reference coordinate system is commonly placed onto the sample surface, with z being normal to the surface, x along the beam direction and y perpendicular to the xz plane. When placing the 2D detector rather close to the sample (around 100 mm), GIWAXS patterns can be observed. GIWAXS probes the crystalline part of the sample and results in a 2D diffraction pattern on the detector. Questions that aim at texture or morphology analysis can only be partially answered by XRD, since only a small region around $q_r = \sqrt{q_x^2 + q_y^2} \approx 0$ is probed. In GIWAXS, however, a full 2D plane in q_r and q_z is recorded. The image on the detector is a result of the orientation sphere of the reciprocal lattice points cutting the Ewald's sphere. Unfortunately, the projection onto a 2D grid results in a range of missing q values, because $q_x \neq 0$. The usual 2D representation in reciprocal space plots the momentum change q_r versus the momentum change in z -direction q_z . Thus, in addition to the classical crystal structure, it can give information about the preferential orientation or texture of crystallites on the sample. Diffraction peaks and rings are labeled in analogy to XRD patterns. From the width of the Bragg diffraction peaks and rings the upper limit for crystallite size can be extracted using the Debye–Scherrer equation.⁷²⁶ Bragg spots can arise for highly ordered systems with long-range order, *e.g.*, single crystals or ordered superlattice diffraction of NCs, due to distinct points in the reciprocal lattice space of those systems. In contrast, isotropic orientation of the crystallites results in a powder scattering pattern, which is identified by the ring-shaped and uniform intensity distribution on the 2D detector.

When moving the 2D detector to larger distances on the order of 1–4 m, a GISAXS signal can be recorded. GISAXS probes distances on the mesoscale (nanometer regime) and is commonly used to investigate the morphology, *i.e.*, domain sizes and interdomain distances of thin films or superstructures of NCs. Not only the crystalline parts of the sample contribute to the scattering, since GISAXS probes the dispersion of the sample, which in turn is related to the scattering length density (SLD). SLD is a material-specific property. Refraction inside

the film leads to enhanced out-coupling under the critical angle of the thin film (so-called Yoneda peak). By analyzing this material-sensitive Yoneda region by horizontal line cuts (in q_y direction), material-specific structure information is accessible. For the analysis commonly the so-called distorted wave Born approximation (DWBA) is combined with several approximations such as the effective interface approximation (EIA) and the local monodisperse approximation (LMA). For more information the reader is referred to the literature.^{727,728} In addition, GISAXS patterns of highly ordered systems show Bragg peaks similar to GIWAXS, which, however, originate from a larger-scale structure as compared to GIWAXS.^{729–733}

1D X-ray Diffraction Measurements. Common XRD measurements with 1D detectors are probably the most frequently used X-ray scattering technique and available in many laboratories at moderate cost. The collection of XRD patterns can be a powerful and comparatively easy tool to identify and distinguish phases in a sample. A complete measurement can often be conducted in less than 1 h including sample preparation and measurement setup. Measurements of thin films, *e.g.*, when dealing with PeNCs deposited on a substrate, are possible using the Bragg–Brentano geometry.^{80,315,450,734} Straightforward studies employ *ex situ* XRD measurements. By comparing XRD patterns to libraries, previous measurements, or literature, crystalline phases can be identified with a high degree of certainty.^{223,274,450,606,681,735,736} For example, Bertolotti *et al.* used X-ray scattering techniques to analyze the long sought after crystal structure of thin films of CsPbBr_3 NPs.²¹⁰ The high asymmetry of NPs favors narrow-band emission acting as nanowells with well-defined dimensions and low variation, thus resulting in discrete band gaps, which are very beneficial for LED application. The crystal structure of NPs is not easily accessible because of their quasi-2D shape. In their study, a combination of low- and high-angle XRD and wide-angle X-ray total scattering (WAXSTS) was used. The high-angle XRD region interestingly suggested an orthorhombic crystal structure as shown in Figure 83f. The result was confirmed *via* Debye scattering equation modeling.^{726,737,738} Discriminating between different phases—even for small crystallites like

NPIs—is an important feature of X-ray scattering by accessing a statistically relevant ensemble of crystallites. The low-angle region in XRD on the other hand, gives information about large distances present in the structure. In this case, it revealed interplatelet distances as shown in Figure 83e. The first peak appeared at $q = 4\pi \sin \theta/\lambda = 0.097 \text{ \AA}^{-1}$, which corresponds to a distance of $d_1 = 64.90 \text{ \AA}$. The high degree of long-range ordering was confirmed by the high number of harmonics toward higher 2θ values marked with d_n in Figure 83f.

Time-Dependent XRD Studies. To investigate kinetic changes, time-dependent XRD measurement protocols are well-suited. This is especially useful for degradation studies that occur over many hours up to months, and the same measurement is repeated at certain intervals. Numerous stability related studies were done on perovskite NC systems and examined by time-dependent XRD studies.^{315,607,736,739} For example, MAPbBr₃ perovskite NCs can be effectively stabilized by essential amino acids as identified by an unchanged XRD pattern over 6 months.⁷³⁵ CsPbBr₃ NCs for white LEDs showed higher resistance against heat and moisture-induced degradation by coating with alkyl phosphate²⁷⁴ and CsPbX₃ NCs were effectively stabilized by a PMMA matrix as shown by time-dependent XRD studies over several days in 80% relative humidity.⁷³⁹

A different approach toward stabilizing CsPbI₃ was reported by Akkerman *et al.* and confirmed by time-dependent XRD measurements.⁶⁰⁷ It is well-known that the stability of the cubic perovskite α -phase is connected to the Goldschmidt tolerance factor and thus the stability can be tuned by site occupation substitution.⁷⁴⁰ Pristine CsPbI₃ suffers from poor stability and is unstable in air. The cubic α -phase decomposes rapidly (within days) into the yellow δ -phase, and corresponding time-dependent XRD data are shown in Figure 83c,d. To obtain stable cubic α -CsPbI₃, Pb⁺ was partially replaced by Mn²⁺ without significant changes to the crystal structure and, more importantly, without inducing significant changes in PL, trPL, and absorption properties of the material, as was shown by Liu *et al.*⁶⁰⁶ Klimov *et al.* showed that Mn²⁺ doping can even be beneficial for its emission properties.⁶⁰⁵ By adding MnI₂ to the precursor solution, alloying could be achieved by Akkerman *et al.* resulting in a cubic drop-cast CsPb_xMn_{1-x}I₃ phase. Meanwhile, the octahedral (Pb/Mn)O₆ geometry was preserved. The partial substitution of Pb²⁺ with Mn²⁺ led to a small reduction in unit cell size and more favorable Goldschmidt tolerance factor for a cubic system (see also previous sections on doping/alloying of NCs). Thus, the structure factor of the crystallographic unit cell changes, which resulted in a changed X-ray diffraction pattern. The decrease in unit cell was verified by XRD measurements reported in Figure 83b. CsPb_xMn_{1-x}I₃ showed increased stability as proven by time-dependent XRD measurement over the course of 4 weeks. In Figure 83d the partial transition toward the orthorhombic δ -phase can be seen starting on day 5 at $\sim 25\text{--}28^\circ 2\theta$. As predicted by DFT calculations a lattice contraction of around 1% was observed in XRD (cf. Figure 83b) for the chemical composition CsPb_{0.91}Mn_{0.09}I₃ resulting in decreased metal–iodine bonds.

Challenging for PeNCs, especially for CsPbI₃ NCs, is the poor stability against illumination. Boote *et al.* followed the degradation of drop-cast CsPbX₃ NCs thin films by time-dependent XRD for up to 16 h under 1 sun irradiation and ambient conditions.⁷³⁶ They found that CsPbBr₃ was phase-stable (orthorhombic γ -phase) under 1 sun illumination for up

to 16 h and when heating up to 250 °C. CsPbI₃, however, was most unstable in the CsPbX₃ series as the nonluminescent yellow phase appeared, as can be identified by decreasing Bragg diffraction intensity, which indicated decomposition into a noncrystalline or amorphous phase.⁷³⁶ However, after some hours of illumination and before the loss of crystallinity occurred, CsPbCl₃ and CsPbBr₃ showed an increased intensity and decreased fwhm of the (100) and (200) reflexes. This led to the conclusion of crystal growth and possibly oriented crystal growth with a changed preferential orientation of the NCs. However, XRD by itself is only partly able to elucidate the texture of an ensemble of crystallites. Preferential orientation is better probed by (GI)WAXS, which is described below. CsPbI₃ thin films washed with methyl acetate solution, for example, showed no change in Bragg peak intensity and were stable under continuous illumination.⁷³² XRD confirmed the same phase and no observable crystallographic changes under illumination. This highlights the importance of surface quality in perovskite NCs and their influence on the PeNCs stability.

XRD studies can also help to elucidate degradation mechanisms. It is known that CsPbBr₃ degrades to a yellow phase under illumination, which is accompanied by a strong PL-quenching, thereby decreasing the EQE of an LED-device drastically. Huang *et al.* carried out studies with different stress factors on the device, *e.g.*, illumination, oxygen, humidity and temperature.²²³ Illumination of 175 mW/cm² for 8 h led to a color change of the thin film from green to yellow. The degradation was tracked using time-dependent XRD measurements. The cubic (100) and (200) Bragg reflexes of the perovskite NCs first broadened and then increased in intensity and sharpness. This indicated a crystal growth and thus was correlated with an observed PL red shift. Under higher illumination strength of 350 mW/cm² the degradation species PbO was identified *via* XRD after 8 h. The driving force of degradation was determined to be oxidation (by oxygen) in combination with illumination strength and moisture, which seemed to support ion migration in crystal growth. Supported by XRD analysis, it was shown that under oxygen stress but no illumination no yellow phase and no PL loss occurred. Li *et al.* showed by XRD analysis that cubic CsPbBr₃ NC-495 thin films also degraded into PbCO₃ and PbO and Cs₄PbBr₆ under illumination in ambient conditions.⁷⁴¹ Larger NC-520 thin films did not decompose within 20 h of illumination.

2D GIXS Imaging. Applying Advanced X-ray Scattering Techniques. When texture and morphology information about the sample are of critical interest, XRD can only supply insufficient information, since it only provides information along $q_z \approx 0$. For texture and/or morphology investigations, a larger q -space needs to be probed. As described above, small- and wide-angle X-ray scattering onto a 2D detector can be the solution to this problem. Details about those measurement techniques are described above.

For example, Zhu *et al.* investigated the phase transitions of FAPbX₃ NCs, X = Cl, Br, I, by *in situ* WAXS and UV/vis measurements during the application of pressure in the range from 0 to 13.4 GPa.⁷⁴² Pressure was applied using a customized diamond anvil cell that enabled WAXS measurements at a synchrotron at the same time. Radial integration of (GI)WAXS images lead to a pseudo-XRD plot (signal intensity *vs* q) that can be indexed in analogy to XRD patterns. Indexing the cut at ambient conditions showed a cubic space group ($Pm\bar{3}m$) and a lattice constant of $a = 6.35 \text{ \AA}$. While increasing

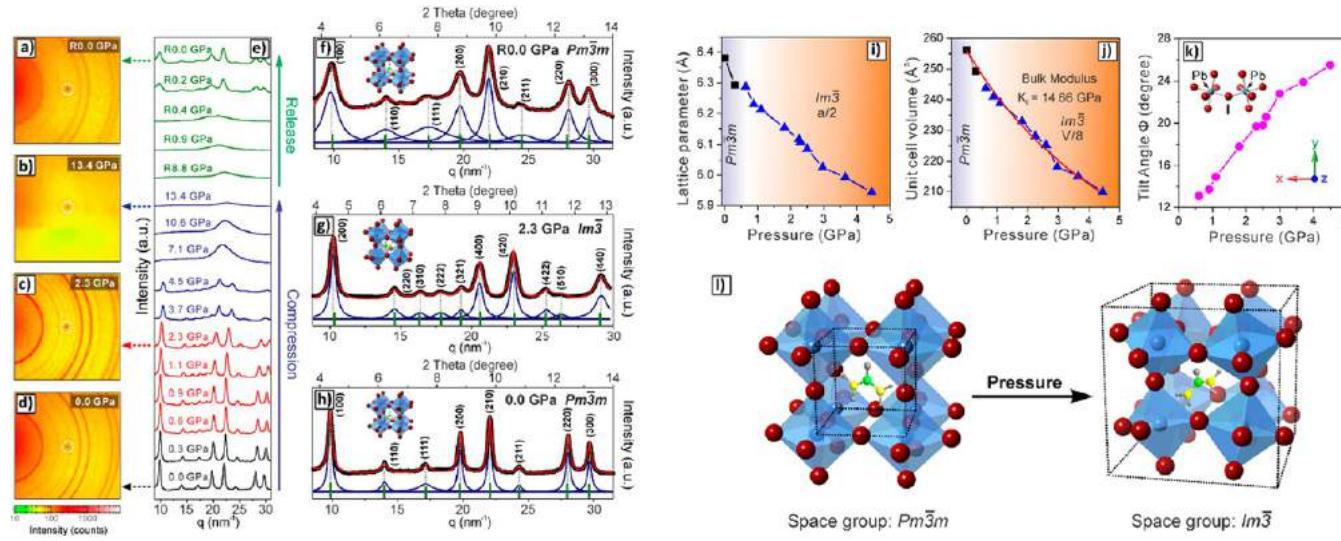


Figure 84. (a–d) *In situ* GIWAXS patterns of FAPbI₃ NCs during compression and subsequent decompression with (e) corresponding pseudo-XRD patterns (radially integrated GIWAXS images). White circles represent noise. (f–h) Fitted and indexed pseudo-XRD patterns with structure representation and corresponding calculated reflex positions. (i–k) Derived lattice parameters, unit cell volume, and octahedral tilt angle evolutions depending on pressure. (l) Schematic representation of the structural changes occurring during pressure increase. The [PbI₆]⁴⁻ octahedron tilts along the cubic [111] direction. Reproduced from ref 742. Copyright 2018 American Chemical Society.

the pressure the WAXS pattern changed. First, additional Bragg rings appeared as seen in Figure 84a–d, which was attributed to a different cubic phase ($Im\bar{3}$). Corresponding pseudo-XRD patterns are shown in Figure 84e. Further increase in pressure led to increased tilting of the [PbI₆]⁴⁻ octahedron (cf. Figure 84f–h) and increasing fwhm of the Bragg rings. The latter usually indicates smaller crystallites or a loss in crystallinity. As expected, a decrease in lattice parameters was observed (red-shifted q values). Before the sample finally transformed into the amorphous state, degradation into the orthorhombic phase ($Pnma$) was observed. The amorphous state was reversible when decreasing the pressure below 0.4 GPa. At this point, a fast reordering into the original cubic $Pm\bar{3}m$ phase occurred. However, the Bragg rings showed a broadening compared to the original sample at ambient conditions, indicating a slight loss in crystallinity of the FAPbI₃ NC film. Often scanning electron microscopy or transmission electron microscopy measurements are chosen to verify and improve the structure model developed through X-ray scattering methods. With TEM measurements, it was confirmed that no significant change in particle size and shape was induced by the pressure cycle. The complete lattice parameter and unit cell volume evolution as deduced from WAXS analysis is plotted in Figure 84i–k. The corresponding tilt of the [PbI₆]⁴⁻ octahedron is shown in Figure 84l. *In situ* PL and UV/vis measurements showed a pressure tunable band gap between 1.44 and 2.17 eV. This WAXS study successfully correlated structural changes to optoelectronic properties that might be vital for further research and the development of industrial production techniques. The results may influence the fine-tuning of the band gap for applications in optoelectronic devices like PV or LEDs.

Investigation of Superstructures by Advanced X-ray Scattering Techniques. Perovskite materials can be driven to self-assembly into 1D, 2D or 3D superlattices which has given rise to focused research on targeted functionalization of low dimensional perovskites and perovskite NC superlattice

structures.^{160,319,677,684,716,743–747} Improved strategies to control shape and size have been found in recent years and targeted tuning is within reach.^{319,748} As more methods for self-assembly and directed superlattice growth of NCs become available also the need for more detailed structural, superstructural and morphological characterization techniques arises. Long-range ordering of the NCs leads to a scattering signal. However, depending on the magnitude of the superlattice parameters, too long distances cannot be probed by conventional XRD. Long distances, corresponding to exceedingly small diffraction angles of less than 2° 2θ are better accessible by increasing the sample detector distance to several meters. (GI)SAXS is a suitable tool to investigate superlattice ensembles revealing information in q_y and q_z direction.^{677,724,744,749}

Horizontal line cuts can be performed on the 2D GISAXS data in the Yoneda region, which gives information about the typical stacking distances present in the sample. From the q ratio of those peaks a first structure model can be derived, e.g., from the q ratios $q:\sqrt{q}:2q$ for a simple cubic superlattice structure.^{191,196,684} Further information about GISAXS interpretation and morphological modeling can be found above. In particular, in combination with TEM/HRTEM and fast Fourier transform (FFT) analysis of real-space imaging, (GI)SAXS can give precise information about superlattice stacking, as explained above.¹⁶⁰ The interplay between superstructure and crystal structure changes, and optoelectronic properties is of key interest for optoelectronic device research. The combination of *in situ* (GI)WAXS and (GI)SAXS can be immensely powerful to track phase transition and superlattice changes simultaneously. Real-space methods like SEM/TEM/STM can be used complementary to reciprocal space imaging techniques and probe local areas and ensemble information, respectively.⁷⁵⁰

For example, Zhang *et al.* investigated the thermally induced crystal and superstructural changes of luminescent cuboidal MAPbI₃ NCs by *in situ* GISAXS and GIWAXS imaging.¹⁶⁰

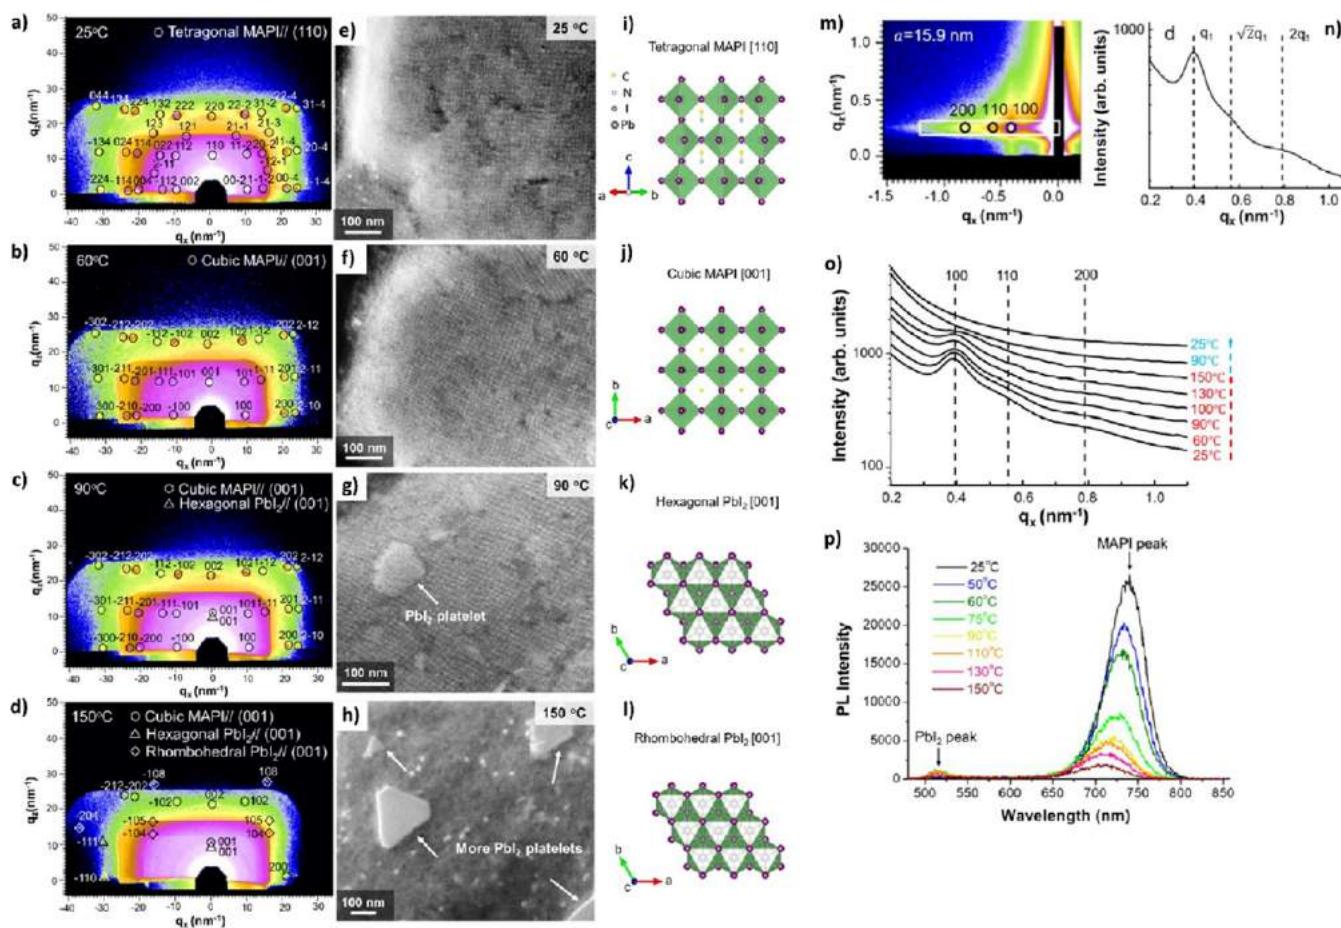


Figure 85. (a–d) *In situ* GIWAXS images of MAPbI₃ NCs heated to 150 °C. The attenuation on the side is due to experimental restrictions. The pattern suggests high ordering with the tetragonal (110) plane oriented parallel to the substrate. A phase transition from tetragonal to cubic is observed around 60 °C. At higher temperatures, hexagonal and rhombohedral PbI₂ can be identified as a degradation product. (e–h) Corresponding SEM images and (i–l) corresponding derived structure representations. (m,n) GISAXS image and azimuthal cut to determine the cubic superstructure with a superlattice constant of 15.9 nm. The three largest distances are marked. (o) Horizontal GISAXS cuts (along q_x), showing a clear loss in ordering around 150 °C. The diffraction peaks stem from a cubic superlattice. (p) PL emission spectra taken with an excitation wavelength of 442 nm. Reproduced from ref 160. Copyright 2019 American Chemical Society.

They found that the chosen evaporation method formed MAPbI₃ NC films with an ordered superlattice. In Figure 85m, a GISAXS image of MAPbI₃ NCs is shown which exhibits distinct in-plane features that can be indexed to a cubic superlattice. A horizontal line cut (cf. Figure 85n) shows a distinct peak at ~ 0.4 nm⁻¹, which corresponds to a superlattice constant of around 15.9 nm. GISAXS images were taken during the heating and cooling process and an evolution of cuts is shown in Figure 85o. Thereby the authors could show that the ordering of the lattice persists under elevated temperatures until approximately 150 °C. This agreed with steadily decreasing PL intensity, as shown in Figure 85p. GIWAXS patterns (cf. Figure 85a) were indexed to a tetragonal space group with an orientation of mainly the (110) plane parallel to the substrate. Distinct Bragg spots were visible in the GIWAXS pattern, which agreed with the high ordering of a superlattice. Upon heating to 60 °C, a phase transition from tetragonal to cubic was observed. *In situ* GIWAXS patterns, corresponding SEM images, and schematic representations are found in Figure 85a–l. When reaching 90 °C, MAPbI₃ NCs started to decompose and highly oriented hexagonal (001)-PbI₂ was found. At 150 °C rhombohedral PbI₂ ($R\bar{3}m$) was visible in the GIWAXS pattern as a

degradation product, and all superlattice ordering was lost (cf. Figure 85d,h,o). In this study, the scattering methods of *in situ* GIWAXS and GISAXS were used in combination with real space SEM/TEM imaging to elucidate the exact phase at varying temperatures, phase transition points, phase changes and preferential orientations of MAPI NCs during thermally induced degradation. Thomas *et al.* applied *in situ* GISAXS and GIWAXS to investigate the heating response of all-inorganic cube-shaped CsPbI₃ NCs under humid conditions in air.¹⁹¹ The perovskite NCs were ligand-stabilized to improve their resistance to moisture degradation by providing a hydrophobic shell. GIXS was used to investigate the degradation and phase transitions as well as loss of superstructural ordering. Indexing of GIWAXS patterns taken at RT showed the γ -orthorhombic phase ($Pbnm$), as shown in Figure 86a,g. The spot-like pattern indicated a high degree of ordering into a superlattice with γ -(110) and γ -(002) being oriented parallel to the substrate. Often, indexing is tested for different space groups to sufficiently explain the full diffraction pattern. In this case, indexing with a cubic phase left some Bragg spots unexplained and therefore the γ -phase was favored. The black γ - or α -phase of CsPbI₃ is the optoelectronically interesting phase as opposed by the yellow δ -phase. *In situ* GIWAXS imaging

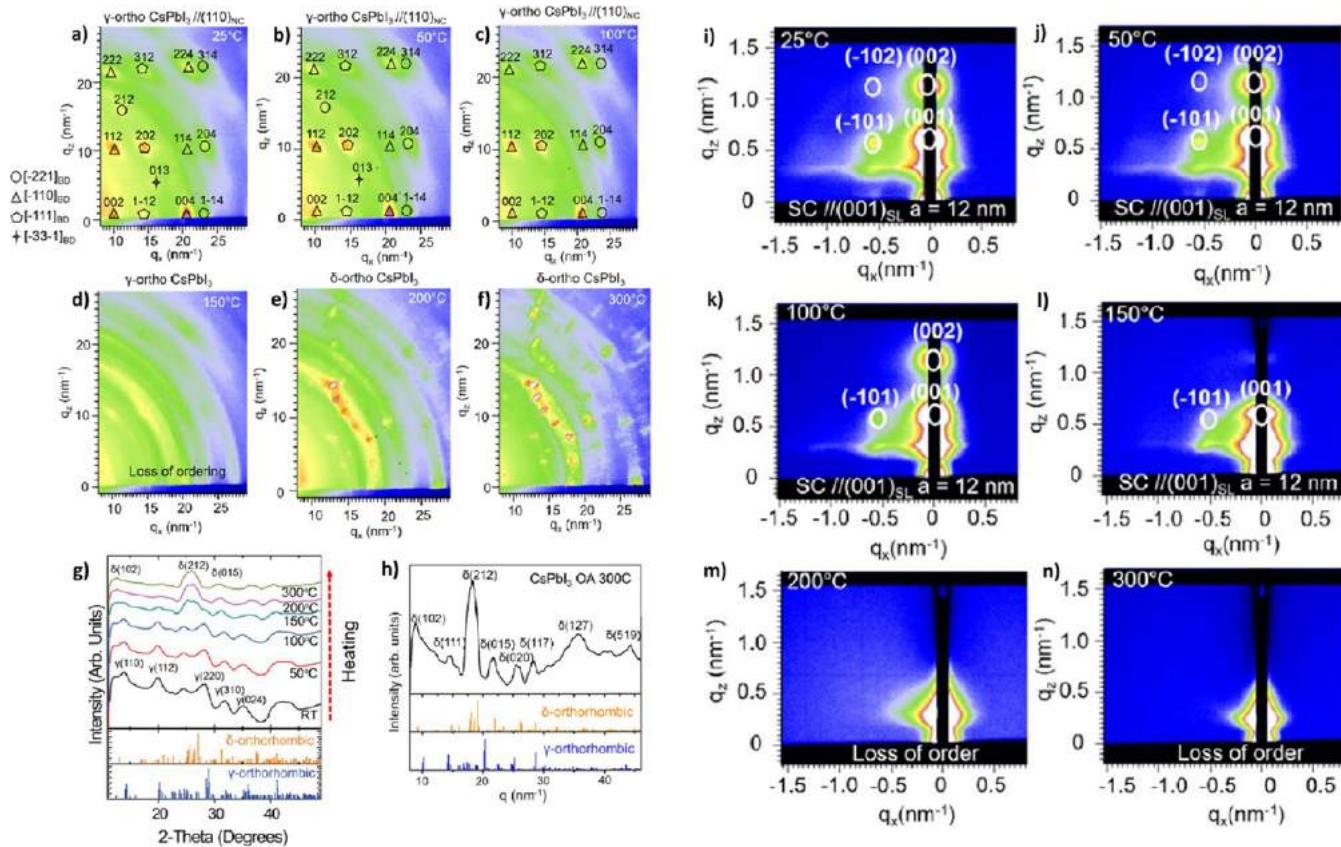


Figure 86. (a–f) *In situ* GIWAXS images of CsPbI_3 NCs taken during heating from RT to 300 °C. Distinct Bragg spots indicate high ordering with the orthorhombic (110) plane parallel to the substrate. (g,h) Pseudo-XRD patterns generated by radial cuts to compare with calculated XRD patterns of the γ - and δ -phase. Bragg peaks of interest are indexed to the corresponding phase. (i–n) *In situ* GISAXS images taken during the heating process. Clear long-range ordering of the NCs into a superstructure is visible. The loss of ordering starts around 150 °C. Reproduced from ref 191. Copyright 2019 American Chemical Society.

while heating $\gamma\text{-CsPbI}_3$ from RT to 300 °C under 40% relative humidity, revealed the γ - to δ -phase transition occurring at ~ 150 °C (cf. Figure 86a–h). GISAXS suggested a simple cubic superstructure with a lattice spacing of 12 nm and (001)_{SL} orientation (cf. Figure 86i–n). A complete loss of the cubic superlattice ordering was observed at 200 °C. Whether the phase transition leads to a loss in superlattice ordering or whether a loss in ordering makes a phase change more favorable is difficult to tell. Thomas *et al.* believe that the main driving force was the thermally induced loss in surface-capping ligands.

GIXS can also be coupled to other *in situ* techniques like TEM, PL or UV/vis, which can be a powerful approach to investigate degradation and structure–function relations. For example, Zhang *et al.* applied a combination of HRTEM/FFT and GISAXS/GIWAXS imaging to lead-free cubic $\text{Cs}_2\text{AgBiBr}_6$ perovskite NCs.¹⁹³ Disintegration of the superlattice was observed around 200 °C and total loss of ordering of the cubic superlattice was reached at 250 °C. Jurow *et al.* used GISAXS to find correlation distances of 3.8 nm in q_z direction of CsPbBr_3 NCs when tuning the transition dipole moment for improved optical characteristics.⁷⁵¹ An interesting alternative to (GI)SAXS superlattice analysis is wide-angle parallel beam X-ray scattering as done by Toso *et al.*⁶⁹² They used the fact that highly ordered CsPbBr_3 NCs form superlattice scattering planes for previously diffracted X-rays that stem from scattering on crystal lattice planes. This interference gives rise to equally spaced satellite peaks and its position is given by

$q_n = 2\pi n / \Lambda$, with Λ being the average superlattice spacing. With this method, an average spacing of $\Lambda \approx 12.2$ nm was found.

X-ray Scattering on Colloidal Dispersions. X-ray scattering is not limited to solid bulks or thin films. Colloidal perovskite NCs in solution can also be investigated by scattering techniques to give insight into the crystal structure and morphology. Precursor engineering has been an important, though not very precise nor predictable method to optimize perovskite materials.⁷⁵² For example, Pratap *et al.* investigated colloidal perovskite precursor dispersions by GIWAXS and UV/vis and found four stages of thin-film formation: nanoparticles in solution, nanoparticle growth, formation of aggregates and complex clusters, and fragmentation of large aggregates.⁷⁵³ Thus, the key steps in thin-film formation for device fabrication could be looked at in detail using a combination of scattering techniques and optical measurements. Van der Burgt *et al.* used transmission SAXS to monitor the formation of perovskite supraparticles in solution (inside a quartz capillary) and were able to prove that the addition of methyl acetate triggered the formation of supraparticles over the course of several days.⁶⁸⁴

Summary and Outlook for X-ray Scattering Characterization of MHP NCs. X-ray scattering techniques are remarkably useful for analyzing crystal structure, degradation induced phase changes, preferential orientation, crystallinity, morphology, and superstructure of perovskite NCs. As advanced scattering techniques become better understood

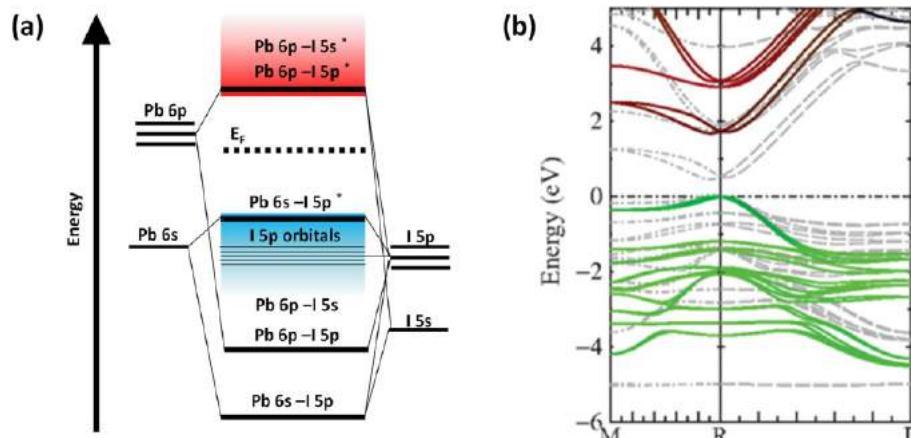


Figure 87. (a) Electronic bands formation in the case of MAPbI₃ perovskites due to hybridization of Pb and I orbitals. Schematic is drawn according to ref 770. (b) Calculated energy band diagram of the 3D CH₃NH₃PbI₃ perovskites under quasiparticle self-consistent GW approximation. Adapted with permission from ref 773. Copyright 2014 American Physical Society.

and availability increases, more and more focus is put on *in situ* GIXS measurements. Grazing-incidence geometry allows for analyzing statistically relevant sample volumes. With small- and wide-angle X-ray scattering (SAXS and WAXS), methods are available to probe length scales from the crystal to the mesoscale. X-ray scattering can be coupled to additional *in situ* compatible measurements, *e.g.*, PL, trPL, or UV/vis. Thereby, a wide-ranging toolbox of techniques is available that allows for flexible and focused investigations of structure–function correlation, especially in the field of PV and LED, where optoelectronic properties are of key interest and often heavily influenced by structure.^{334,754,755} X-ray scattering techniques are being constantly improved and especially image processing and simulation of 2D scattering images from advanced scattering techniques will become increasingly available.^{756–759} *In situ* investigations on deposition techniques well-fitted for industrial purposes, *e.g.*, roll to roll processing, and coupling to advanced experiments for degradation and formation investigations might well be in the focus of future research. However, also more easily accessible X-ray diffraction routinely available at many groups can be greatly beneficial for perovskite NC studies. XRD measurements can be used to provide phase information, phase purity, lattice parameters and can give hints for superstructural arrangements and crystallinity. Thereby, X-ray scattering techniques will help perovskite NC systems to gain even more attention from the scientific community and become increasingly promising for exploring fundamental properties as well industrial applications.^{747,760,761}

OPTICAL PROPERTIES

Linear Absorption and Photoluminescence. MHPs have been known for their intriguing optical and electronic properties that are appealing for low-cost, high-performance optoelectronic devices. These include tunable photoluminescence across the entire visible spectrum, high-color purity, multicolor chromism, high absorption coefficients, high PLQY, and long charge carrier diffusion lengths.^{13,762–764} The band gap of MHPs is easily tunable over UV–vis–near-IR wavelengths by varying the halide compositions (X = I[−], Br[−], Cl[−]).^{14,31,538,765–769} They have been intensely explored in solar energy and light harvesting applications. MHP-based colloidal NCs exhibit high PLQY compared to classical, core-only quantum dots, suggesting the significant reduction of non-

radiative loss channels prevalent in the corresponding bulk MHPs films. In the previous sections, we reviewed the shape and composition-controlled synthesis of perovskite NCs. In this section, we focus on their optical properties. We start by briefly reviewing the optical properties of bulk MHPs and then review how they change when the size of the crystals decreases to the nanoscale. We further discuss the phenomena which manifest only in NCs, such as quantum confinement. As discussed in other sections, the advances in the synthesis enable the preparation of MHP NCs with highly controlled size, shape and surface properties. These NCs provide a very convenient platform to study the optical properties of MHPs which are not specific only to nanoscale. In this context, we review the optical, spin and electronic properties of colloidal MHP NCs and how they can be used to reveal insights into the properties of their bulk counterparts.

Electronic Band Structure. In lead-based MHP, the conduction band consists of σ -antibonding Pb 6p orbitals and halide np orbitals, hence possesses a p-type character (Figure 87a). The electronic configuration of Pb(II) is 6s²6p⁰, and it is np⁶ for halides (where n = 3–5 from Cl to I).^{770,771} The valence band in MHP is made of σ -antibonding Pb 6s and halide np orbitals, conferring the band a partial s-type character. In effect, the transition from the valence to the conduction band is dipole allowed.⁷⁷² Figure 87b shows the calculated electronic band structure of the 3D MAPbI₃ perovskites under quasiparticle self-consistent GW approximation (QS_GW).⁷⁷³ The color of the bands corresponds to their orbital characters where green, red and blue depicts I 5p, Pb 6p, and Pb 6s orbitals, respectively. M and R points are the zone-boundary points close to (1/2,1/2,0) and (1/2,1/2,1/2), respectively. MAPbI₃ has a direct band gap with the CBM and VBM lying at the R point of the Brillouin zone. The VBM and CBM are shifted slightly from R as a consequence of spin–orbit coupling (SOC). As lead and iodine are heavy elements, SOC is large in MHPs and has a significant effect in their optical and electronic properties. Even *et al.* reported that the exclusion of SOC severely underestimates the band gap calculation in MHPs.⁷⁷⁴ Importantly, the SOC strongly influences the width of the band gap. Specifically, the optical band gaps in MAPbI₃ and MAPbBr₃ shrink by 0.5 and 0.8 eV, respectively, when SOC is taken into account as compared to the band gap calculation without considering SOC.⁷⁷⁴ Due to

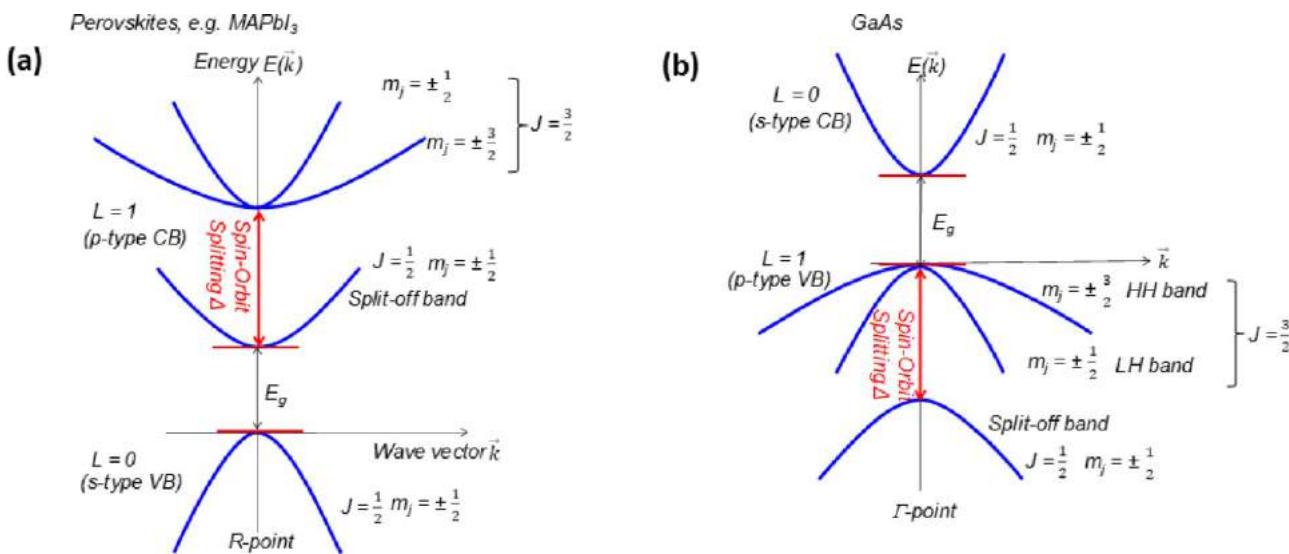


Figure 88. Schematic representation of the electronic band structure of (a) lead-based MHP and (b) GaAs. The VB of GaAs consists of heavy hole (HH) and light hole (LH) bands, along with a split-off band. On the contrary, MHP has an inverted band structure with the split-off band being the CB.

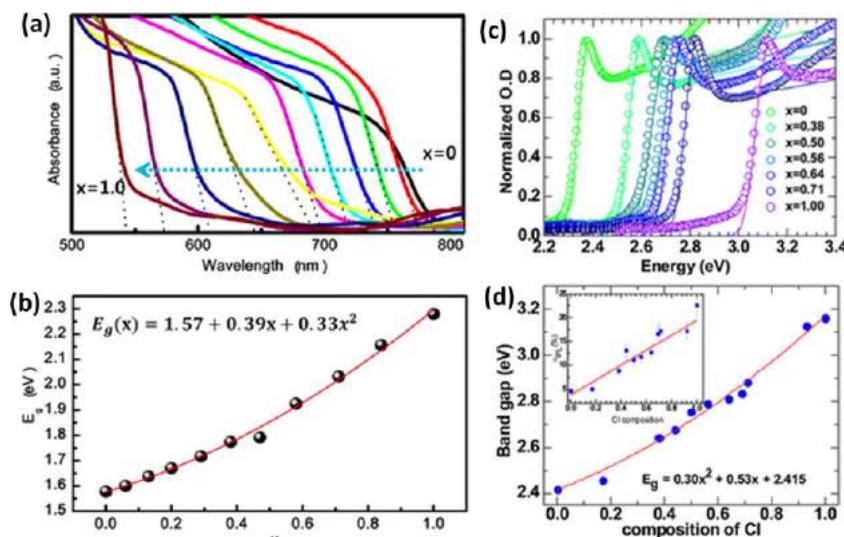


Figure 89. (a) Absorption spectra of FTO/bl-TiO₂/mp-TiO₂/ MAPb(I_{1-x}Br_x)₃/Au cells, where the band gap shifts toward lower wavelengths with increasing Br substitution. (b) Composition-dependent band gap follows a quadratic relationship with respect to Br concentration (x). Adapted from ref 765. Copyright 2013 American Chemical Society. (c) Absorption spectra of MAPb(Br_{1-x}Cl_x)₃ bulk thin films, where x varies from 0 (MAPbBr₃) to 1 (in the case of MAPbCl₃). The circles correspond to the experimental data, whereas the solid lines are simulated absorption spectra using the Sommerfeld model, considering the enhancement in the absorption coefficient by taking into account for the Coulomb field of the exciton. (d) Quadratic behavior of the band gap with Cl composition in the case of MAPb(Br_{1-x}Cl_x)₃ thin films. Adapted from ref 768. Copyright 2015 American Chemical Society.

its p-type character, the conduction band is affected strongly due to SOC while the valence band remains nearly unaffected. This leads to two-fold degenerate split-off (SO) states representing the CBM in the lead-based MHPs (Figure 88a).⁷⁷⁴

The electronic band structure of MHP is inverted compared to the classical semiconductor such as GaAs (Figure 88b). In GaAs the CBM and VBM lie at the Γ point of the Brillouin zone where the CB is s-type with orbital angular momentum $L = 0$ and the VB is p-type with $L = 1$. The VB in GaAs consists of heavy hole (HH) band and light hole (LH) band with total spin angular momentum $J = 3/2$ and magnetic quantum number $m_j = \pm 3/2$ for HH and $\pm 1/2$ for LH. The split off

band with $J = 1/2$ lies below the LH band separated by the spin-orbit coupling induced splitting (Δ). In the case of MHP, the VB is s-type, whereas the CB is p-type where the split off band ($J = 1/2$) represents the CB. Importantly, the valence and the conduction bands in MAPbI₃ have high-energy dispersion in k -space which gives rise to small hole and electron effective masses. The small carrier effective masses are consistent with high mobilities and long carrier diffusion lengths in this material.⁷⁷³

Optical Band Gap. Since the top of the valence band in MHPs are dominated by the halide p orbitals (Figure 87b) with only minor contributions from antibonding Pb 6s² orbitals, the valence band position becomes sensitive to the

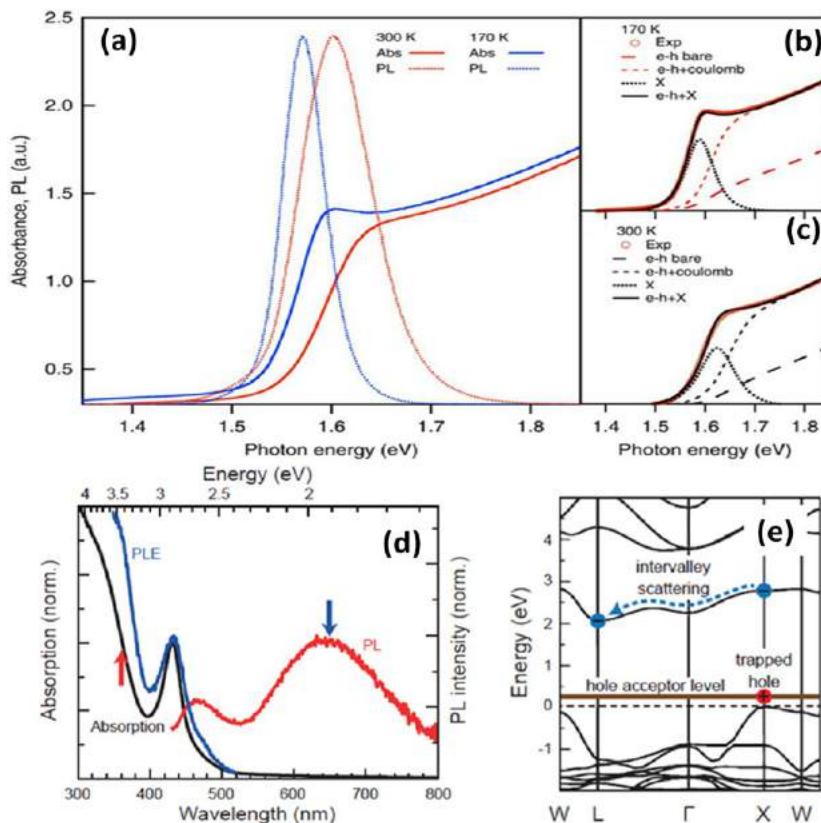


Figure 90. (a) Absorption (continuous line) and PL (dashed line) spectra in MAPbI₃ films, recorded at 300 and 170 K. Elliot fits to the experimental absorption spectra at (b) 170 and (c) 300 K. Excitonic and band to band oscillator strength contributions calculated by taking into account Coulomb interaction according to Elliott's theory of Wannier excitons are shown in (b) and (c). The excitonic contribution is enhanced at low temperature. Adapted with permission from ref 780. Copyright 2014 Nature Publishing Group, a division of Macmillan Publishers Limited. All rights reserved. (d) Linear absorption, PL, and PLE (detected at 650 nm) spectra of DP NCs dispersed in toluene. (e) Electronic band structure of Cs₂AgBiBr₆ double perovskite. The blue and red circles represent the electron and trapped hole, where the brown solid line indicates the hole acceptor level. Adapted from ref 779. Copyright 2020 American Chemical Society.

choice of halide ions. The band gap increases from I- to Br- to Cl-based MHPs. The increase in band gap is predominately driven by the downshift of valence band while the conduction band upshift is less pronounced.⁷⁷¹ Noh *et al.* showed optical band gap tuning in mixed-halide MAPb(I_{1-x}Br_x)₃ perovskites by changing the compositions of I and Br ions.⁷⁶⁵ Figure 89a shows the corresponding experimental absorption spectra of mp-TiO₂/MAPb(I_{1-x}Br_x)₃ (0 ≤ x ≤ 1). The absorption onsets of mp-TiO₂/MAPb(I_{1-x}Br_x)₃ vary from 786 nm (1.58 eV) to 544 nm (2.28 eV), resulting in wide color tunability. The estimated band gaps from the absorption onsets were observed to follow a quadratic relationship with halide compositions (Figure 89b). The absorption spectra increases sharply at the optical band-edge consistent with a direct band gap with allowed transitions. While in the iodide, the excitonic contribution is not much pronounced, and it becomes prominent at the optical band-edge when moving from I- to Br- to Cl-based MHPs (Figure 89c). Kumawat *et al.* calculated the band gap in MAPb(Br_{1-x}Cl_x)₃ by considering the effect of excitonic contribution at the band-edge using the Sommerfeld model. The band gap increases from 2.4 eV for MAPbBr₃ to 3.1 eV for MAPbCl₃.⁷⁶⁸ Similar to the case of I-Br-based mixed-halide MHPs, the band gap tuning in Br-Cl-based MHPs varies in a quadratic fashion with the Cl composition (Figure 89d). Similar to MA-based MHPs, FA- and Cs-based LHPs also exhibit similar trends of band gap tuning with the change in halide compositions.

It is important to note that A-site cations such as MA, FA, or Cs, do not contribute to the electronic band gap directly but can still influence the crystal structure *via* rotation of Pb-X-Pb bond angles and thus, indirectly modify the band gap.^{775–777} Beyond lead-based systems, there has been extensive work on MHPs based on Sn and Ge, as well as halide double perovskites and other perovskite-inspired materials (refer to **NANOCRYSTALS OF LEAD-FREE PEROVSKITE-INSPIRED MATERIALS**). The band gap of CsSnX₃ perovskite is lower compared to the Pb²⁺ analogues due to higher electronegativity of Sn ions compared to Pb.^{515,518} Huang *et al.* showed that there is relatively small amount of change in the band gap from CsSnCl₃ to CsSnI₃ compared to Pb-based MHP, due to interatomic Sn s and Sn p character of the VBM and CBM.⁵¹⁹ Unlike Pb²⁺-based MHP, lead-free double perovskites (DP) with stoichiometric formula A₂B^IB^{III}X₆^{183,499,778,779} show weak photoluminescence due to indirect band gap or parity-forbidden direct transitions. Using DFT calculations, Meng *et al.* predicted that, out of nine possible DP, six of them show parity-forbidden direct band gap transitions.⁷⁷⁸

Band Gap Excitation. As observed in Figure 89c, the excitonic transitions at the band gap in MHPs imply considerable Coulomb interactions between the electrons and holes. Therefore, the absorption coefficient does not simply follow the square root dependence as in the case of free electrons and holes. Instead, there is an additional contribution

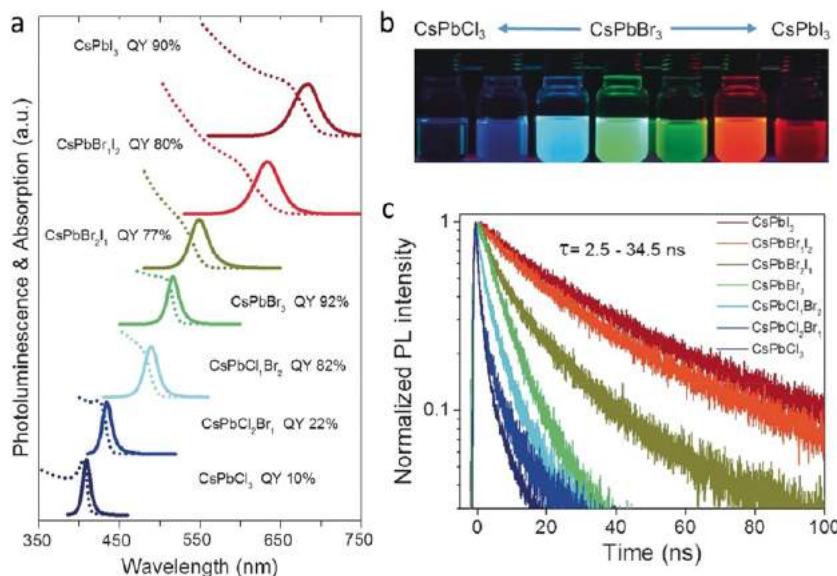


Figure 91. (a) Linear absorption and PL spectra and the corresponding PLQYs of CsPbX_3 NCs of different halide compositions synthesized by ultrasonication approach. (b) Photograph of the corresponding colloidal dispersions in hexane under UV light. (c) PL decay traces of the corresponding NCs. Adapted with permission from ref 30. Copyright 2016 John Wiley & Sons, Inc.

from Sommerfeld enhancement above the band-edge and excitonic transitions below. Therefore, it is appropriate to deconvolute excitonic *versus* continuum transition probabilities.^{768,780} In the case of bulk MHPs, Saba *et al.* used the Elliot theory of Wannier–Mott excitons to model the measured absorption spectra.⁷⁸⁰ Figure 90a shows the linear absorption and emission spectra of MAPbI_3 thin films at 300 and 170 K, respectively, as measured by Saba *et al.*⁷⁸⁰ The excitonic *versus* continuum contributions have been separated out using Elliot model. It was noticed that at lower temperatures the excitonic contribution increases in MHPs (Figure 90b,c).

Similarly to Pb^{2+} -based MHP, the optical band-edge of lead-free double perovskites is also dominated by sharp absorption resonance (Figure 90d).⁷⁷⁹ This optical resonance has been assigned to self-trapped exciton in the case of $\text{Cs}_2\text{AgInCl}_6$.⁴⁹⁹ In the case of $\text{Cs}_2\text{AgBiBr}_6$ double perovskites, Dey *et al.* explained the origin of this sharp optical resonance with the help of the electronic band structure (Figure 90e).⁷⁷⁹ It was demonstrated that it is unlikely that the high effective mass electron along with the low effective mass hole at the direct band gap could lead to a bound state with strong binding energy, because the reduced mass of the electron–hole pair would have been small in such case. Considering the effect of hole trapping by Ag vacancies, they concluded that the bound hole along with the high effective mass electron could lead to a defect bound exciton at the direct band gap. Consequently, the high-energy PL emission close to the optical resonance (Figure 90d) was assigned to the radiative recombination of these direct bound excitons due to their giant oscillator strength. This was corroborated by theoretical calculations in which using ground- and excited-state *ab initio* methods, Palummo *et al.* showed that the first absorption peak in $\text{Cs}_2\text{AgBiBr}_6$ and $\text{Cs}_2\text{In}_2\text{X}_6$ is consistent with bound excitons.⁷⁸¹

Bulk MHPs typically exhibit weak PLQY limiting their light-emitting applications. Crucially, this property is radically changed when moving from bulk to nanocrystals underscoring the effect of the crystal size and interface composition on the optical properties of MHP. Specifically, it has been shown that reducing the crystal size to nanoscale leads to a significant

improvement in PLQY.^{14,25,29,30,169} Since the early report of highly luminescent (PLQY $\sim 80\%$) green emissive MAPbBr_3 colloidal crystals,²⁵ significant research efforts have been devoted to the development of colloidal MHP NCs made of different cation and anion compositions with improved optical properties regarding their stability, PL tunability, PLQY (discussed in previous sections). Similar to their bulk counterparts, the optical band gap and PL emission in colloidal MHP NCs is easily tunable across the visible region of the electromagnetic spectrum by varying the halide composition.^{14,30} For example, colloidal CsPbX_3 NCs synthesized by ultrasonication approach exhibit extremely high PLQYs and tunable emission between 400 and 680 nm by just varying the halide composition (Figure 91a,b). Br- and I-based MHP NCs exhibit near-unity PLQY under optimized synthesis conditions, while the Cl-based MHPs exhibit lower PLQY.^{14,30} The low PLQY of Cl-based perovskites has been attributed to the halide vacancies acting as nonradiative traps. PL decay gets faster going from iodide *via* bromide to chloride-based CPbX_3 perovskite NCs (Figure 91c). The faster PL decay time and low PLQY in the case of Cl-based NCs suggest that they exhibit higher nonradiative rates as compared to the iodide and bromine-based NCs. Nevertheless, it has been shown recently that the PLQY in these perovskites can also be dramatically improved to near-unity by doping with metal halides such as CuCl_2 and MgCl_2 .^{782,783} The origin of the high PLQYs of the colloidal MHPs with respect to the bulk material is still an intensively investigated subject.^{147,784} It is postulated that the increased surface to volume ratio and effective surface passivation with ligand molecules, and thereby a removal of surface traps, causes the increased PLQY of colloidal MHP NCs as compared to their bulk counterparts. A recent study suggested that increased oscillator strength in MHP NCs results in enhanced PLQY when their morphology is tuned from bulk to nanoscale.⁷⁸⁴

Quantum-Confinement Effect on Optical Band Gap. Another important consequence of the reduction in size of the MHP crystals is the manifestation of quantum-confinement effects. Three size ranges may be delimited: (i) when the size is

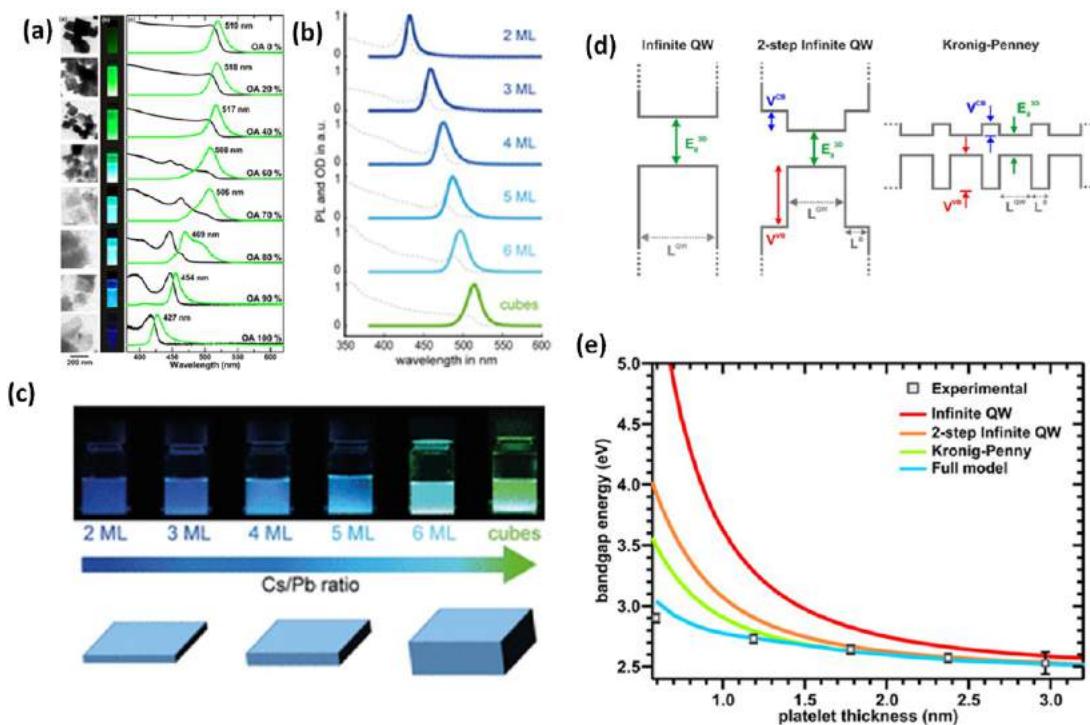


Figure 92. (a) TEM images, pictures of NPI solutions, linear absorption, and PL spectra of MAPbBr₃ NPs. Adapted from ref 16. Copyright 2015 American Chemical Society. (b) Linear absorption and PL spectra of CsPbBr₃ NPs with varying thicknesses. (c) Pictures of CsPbBr₃ NPs and cubes dispersed in hexane under UV-light exposure. The emission wavelength red shifts with increase in monolayer thickness. Panels b and c are adapted from ref 60. Copyright 2018 American Chemical Society. (d) Quantum well models used to reproduce the experimental spectra, as shown in c. (e) Calculation of the energy of perovskite nanplatelets as a function of platelet thickness (solid lines) and the experimentally determined values (gray squares). Panels d and e were adapted from ref 16. Copyright 2015 American Chemical Society.

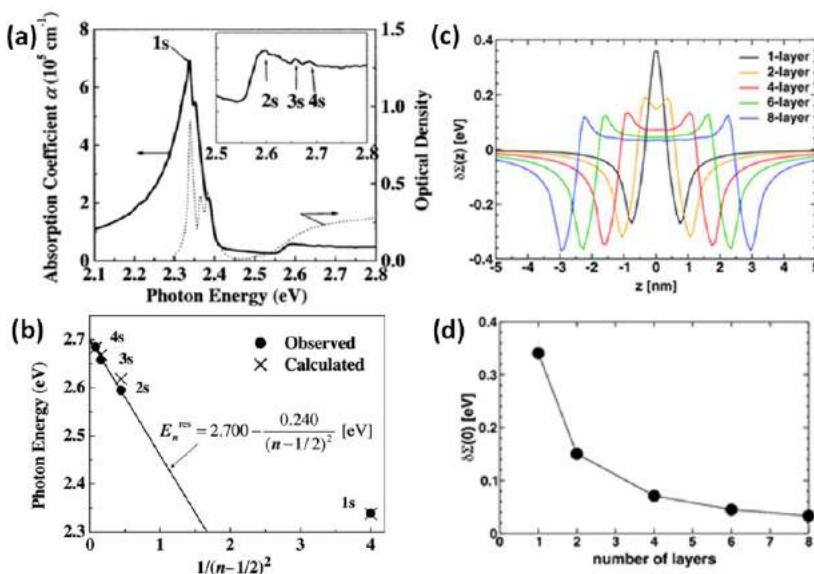


Figure 93. (a) The solid line shows the optical absorption spectrum of a (C₆H₁₃NH₃)₂PbI₄ single crystal at 5 K obtained from the Kramers–Kronig transformation of its reflection spectrum. The inset shows the expansion around 2.6 eV. Dotted line shows the optical absorption spectrum of (C₆H₁₃NH₃)₂PbI₄ polycrystalline film measured at 5 K. (b) Resonance energies of Wannier series excitons in (C₆H₁₃NH₃)₂PbI₄ as a function of $1/(n-1/2)^2$. Closed circles and crosses represent the observed and calculated energies of the excitons, respectively. The solid line shows the fitting based on a simple two-dimensional Wannier exciton model. Panels a and b are adapted with permission from ref 788. Copyright 2005 American Physical Society. (c) Self-energy profile $\delta \Sigma(z)$ for slabs of CH₃NH₃PbI₃. (d) Self-energy taken at the slab center $\delta \Sigma(0)$. Panels c and d are adapted with permission from ref 789. Copyright 2016 Royal Society of Chemistry.

much larger than the exciton Bohr radius ($d \gg a_B$), so that the confinement effects are negligible, (ii) weak confinement

regime when the size is comparable with the exciton Bohr radius, and (iii) strong confinement regime when the exciton

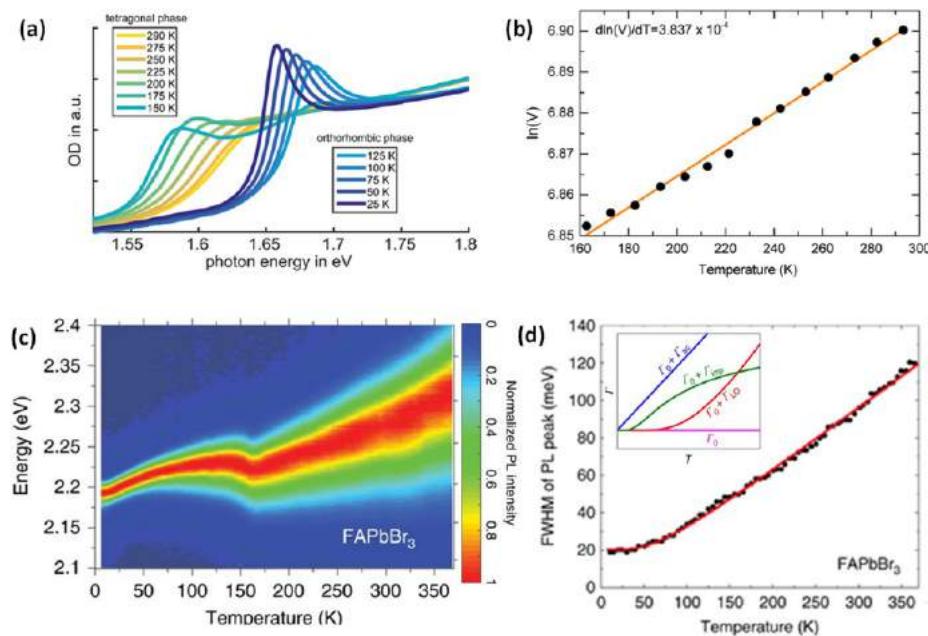


Figure 94. (a) Temperature-dependent absorption spectra on CH₃NH₃PbI₃ nanoplatelets for temperatures of 25 to 290 K. The 1s exciton transition is prominent at low temperature. Adapted from ref 793. Copyright 2017 American Chemical Society. (b) ln of the volume of CH₃NH₃PbI₃ in tetragonal phase as a function of temperature. Solid line is a linear fit representing positive coefficient of thermal expansion. Adapted from ref 794. Copyright 2016 American Chemical Society. (c) Color plot for the normalized steady-state PL spectra of FAPbBr₃ thin film between a temperature range of 10 to 370 K. (d) Corresponding fwhm of the steady-state PL spectra. Panels c and d are adapted with permission under a Creative Commons CC BY license from ref 795. Copyright 2016 The Authors.

Bohr radius is larger than the NC ($a_B \gg d$). Interestingly, the average size distribution of typical colloidal MHP NCs is $\sim 10 \pm 1$ nm which falls under the weak confinement regime where the effect on the band gap is small. Nonetheless, in the strong confinement regime provides a means to effectively tune the band gap in MHPs.^{16,60,138,150,785,786} In the strong quantum-confinement regime, the electron and the hole should be viewed as independent particles and their confinement energies needs to be calculated first before taking into account their Coulomb interaction.⁷⁸⁷

Colloidal 2D perovskite nanoplatelets have been greatly explored to understand the quantum-confinement effects in MHPs (refer to **Nanoplatelets** section for detailed discussion). Sichert *et al.* demonstrated and modeled the two-dimensional quantization behavior and excitonic effects in MHP NPs based on MAPbBr₃ perovskites (Figure 92a).¹⁶ Later, Bohn *et al.* showed precise control over the thickness of CsPbBr₃ perovskite NPs by varying it, from 2 to 6 monolayers (Figure 92b).⁶⁰ The colloidal NPs exhibit sharp optical transitions at the band-edge due to strong quantum-confinement effect. Hence, in 2D perovskite NPs the exciton binding energy enhanced compared to 3D nanocubes.^{16,60} The exciton binding energy in CsPbBr₃ increases from 30 to 280 meV when their dimension changes from 3D nanocubes to 2D NPs with 2 monolayer thickness (Figure 92c).⁶⁰

Sichert *et al.* demonstrated that the simple consideration of an infinite quantum well model (Figure 92d) overestimates the quantization energy compared to the experimentally determined values under the assumption of infinite confinement energy.¹⁶ They successfully modeled the band gap energies for NPs with monolayer numbers (n) = 3, 4, 5, under the approximation of a one-band effective-mass Kronig–Penny model. They observed for thinner NPs (Figure 92e), such as $n = 2$ and $n = 1$ where the exciton binding is very high, the

discrepancies between theory and experiment are quite large.¹⁶ In the case of bulk perovskites with low dielectric constant, Coulomb screening dominates, leading to a reduction of the exciton binding energy. In the case of extremely thin NPs, most of the electric field lines between electron and hole are outside of the platelets where the dielectric constant is low compared to that of the semiconductor platelets, and this minimizes the Coulomb screening and thus enhances the exciton binding energy, accounting for the results obtained for extremely thin platelets.¹⁶

Effect of Dielectric Confinement on Low-Dimensional MHPs. When charge carriers are confined in low dimensional multilayer halide perovskites, their self-energy could be further enhanced by the surrounding polarizability of the perovskite lattice arising due to dielectric inhomogeneity.^{789–791} This effect influences the electron–hole interaction energy, thus giving rise to a strong exciton resonance (Figure 93a). In the case of (C₆H₁₃NH₃)₂PbI₄ crystals⁷⁸⁸ and for bromide compounds (C₄H₉NH₃)₂PbBr₄ and (C₆H₅C₂H₄NH₃)₂PbBr₄),⁷⁹² it was shown that the exciton resonance spectra deviated from the well-known 2D-hydrogen-like series due to the dielectric confinement effect (Figure 93b). Sapiro *et al.* calculated the self-energy profile for MAPbI₃ nanoplatelets (Figure 93c).⁷⁸⁹ The self-energy is equivalent to one-particle electrostatic potential profile acting on a charge carrier in layered heterostructures and calculated by solving the inhomogeneous Poisson equation. The self-energy value is higher at the center of the slab for lower thicknesses due to dielectric confinement effects (Figure 93d).⁷⁸⁹

Effect of Temperature on Optical Transitions. Unlike most conventional semiconductors (e.g., GaAs, GaN, or Si), MHPs show a blue shift in the band gap with increasing temperature (Figure 94a).^{780,794–796} MAPbI₃ undergoes a phase transition from the tetragonal to the orthorhombic phase at temperatures

below 163 K.^{793,794,796} In both phases, the band gap increases with increasing temperature due to a large coefficient of thermal expansion, which results in a positive temperature coefficient of the band gap (Figure 94b).⁷⁹⁴ Singh *et al.* showed that in the case of MAPbI_3 , lattice dilation plays a more significant role compared to electron–phonon coupling.⁷⁹⁴ They determined the volume expansion coefficient of $\text{CH}_3\text{NH}_3\text{PbI}_3$ to be $(1.35 \pm 0.014) \times 10^{-4} \text{ K}^{-1}$ which is 50 times higher than crystalline Si. In contrast to MAPbI_3 and MAPbBr_3 , MAPbCl_3 shows a decrease in the band gap with increasing temperature because electron–phonon coupling dominates over the effects of lattice dilation.⁷⁹⁷ In MHPs, electron–phonon coupling is found to be very strong, in which Fröhlich interactions between carriers and optical phonons are the dominant source of electron–phonon coupling.^{795,798} In the case of vacancy ordered halide perovskites single crystals, such as $\text{Cs}_3\text{Bi}_2\text{I}_9$, $\text{Cs}_3\text{Sb}_2\text{I}_9$, and $\text{Rb}_3\text{Bi}_2\text{I}_9$, the emission process has been explained with self-trapped excitons which arise due to strong electron–phonon coupling inducing the formation of small polarons.⁵⁴¹

In MHP, charge carrier scattering with longitudinal optical (LO) phonons has been shown to cause the broadening of the excitonic absorption⁷⁹³ and photoluminescence peaks (Figure 94d).⁷⁹⁵ In general, impurities or (in the case of NCs) polydispersity can cause the exciton line width to further broaden inhomogeneously (Γ_{inhomo}), as shown in Figure 95a.⁷⁹³ Γ_{inhomo} is a temperature independent quantity whereas

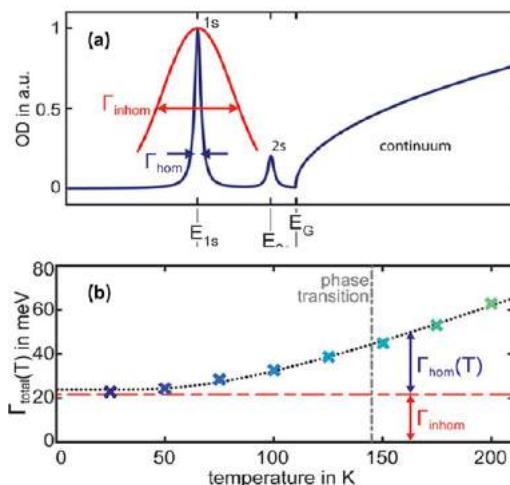


Figure 95. (a) Schematic of the absorption spectrum of one single bulk-like NPI where the homogeneous broadening of the Lorentzian-shaped excitonic peaks is given by Γ_{hom} (dark blue). The excitonic levels (1s, 2s) and the continuum onset are well-separated and easily distinguishable. (b) Total exciton line broadening of the 1s exciton state Γ_{total} ($=\Gamma_{\text{hom}} + \Gamma_{\text{inhomo}}$) as a function of temperature T (<200 K), where the dotted line represents the fitting of the theoretical model considering LO phonons. The Γ_{hom} has been calculated using the exciton dephasing time (T_2) as $\Gamma_{\text{hom}} = 2h/T_2$. Adapted from ref 793. Copyright 2018 American Chemical Society.

Γ_{hom} depends on temperature (Figure 95b). Bohn *et al.* determined the homogeneous line broadening in the case of MAPbI_3 nanoplates using temperature-dependent transient four wave mixing (FWM).⁷⁹³ They determined an exciton dephasing time (T_2) $\sim 800 \pm 20$ fs for the 1s exciton in

MAPbI_3 nanoplates at 25 K, giving rise to $\Gamma_{\text{hom}} = 2\hbar/T_2 = 1.7 \pm 0.1$ meV and $\Gamma_{\text{inhomo}} = 22 \pm 1$ meV.⁷⁹³

Stokes Shift. Quantum-confined (QC) MHP NCs exhibit blue-shifted emission compared to their 3D bulk counterparts. For instance, strongly quantum-confined CsPbBr_3 NCs emit blue photoluminescence, while their 3D counterparts emit green photoluminescence. Brennan *et al.* synthesized CsPbBr_3 nanocubes with size distribution ranging from 13 to 4 nm.⁷⁸⁸ They found that the Stokes shift for CsPbBr_3 nanocubes increased with increasing quantum confinement (or decreasing size).⁷⁸⁸ The Stokes shift was found to decrease from 82 to 20 meV for the CsPbBr_3 nanocubes as the size increased from 4 to 13 nm (Figure 96a,b). The size-dependent Stokes shift has

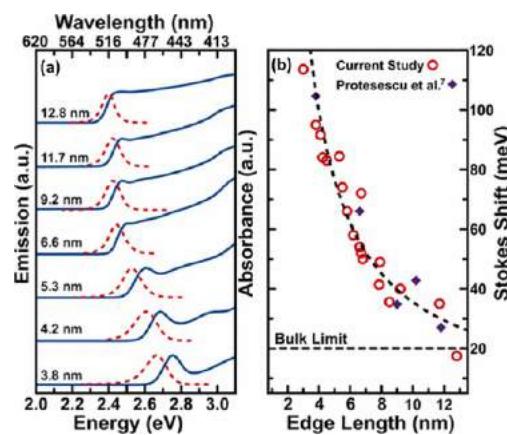


Figure 96. (a) CsPbBr_3 NCs ensemble absorption (solid blue lines) and emission (dashed red lines, $E_{\text{exc}} = 3.543$ eV, $\lambda_{\text{exc}} = 350$ nm) spectra for a series of varying sizes. All absorption/emission spectral pairs are offset for clarity. (b) Corresponding size-dependent Stokes shifts and those extracted from existing literature. Adapted from ref 785. Copyright 2017 American Chemical Society.

been explained by the confinement of the hole state.⁷⁸⁵ For double perovskites, vacancy-ordered halide perovskites, and inorganic zero dimensional tin-halide perovskites $\text{Cs}_{4-x}\text{A}_x\text{Sn}(\text{Br}_{1-y}\text{I}_y)_6$ ($\text{A} = \text{Rb}, \text{K}; x \leq 1, y \leq 1$), the long-lived emission was strongly Stokes-shifted and have been assigned to the formation of self-trapped excitons.^{541,799,800}

Similarly to the band gap width, the Stokes shift for MAPbBr_3 and CsPbBr_3 single crystals has been found to be highly temperature-dependent, as shown by Guo *et al.*⁸⁰¹ They have observed that the luminescence Stokes shifts for MAPbBr_3 and CsPbBr_3 single crystals increased with increasing temperature between 60 and 300 K range. However, below 50 K, the luminescence Stokes shift weakly depended on temperature and decreased as the temperature increased.⁸⁰¹ This temperature-dependent Stokes shift was explained in terms of a classical Debye-like relaxation process of the dielectric response function originating from the anharmonicity of the LO (longitudinal-optical) phonons at about 160 cm^{-1} in the lead bromide sublattice.

Exciton Fine Structure. Excitons are the central emitting species in the semiconductor nanostructures that appear as additional (sometimes sharp) optical transitions at the optical band-edge.^{802–804} The degeneracies of the lowest exciton states are broken by strong exchange interactions, spin–orbit coupling, intrinsic crystal field; nanostructures shape anisotropy giving rise to the multiple splitting of the lowest exciton

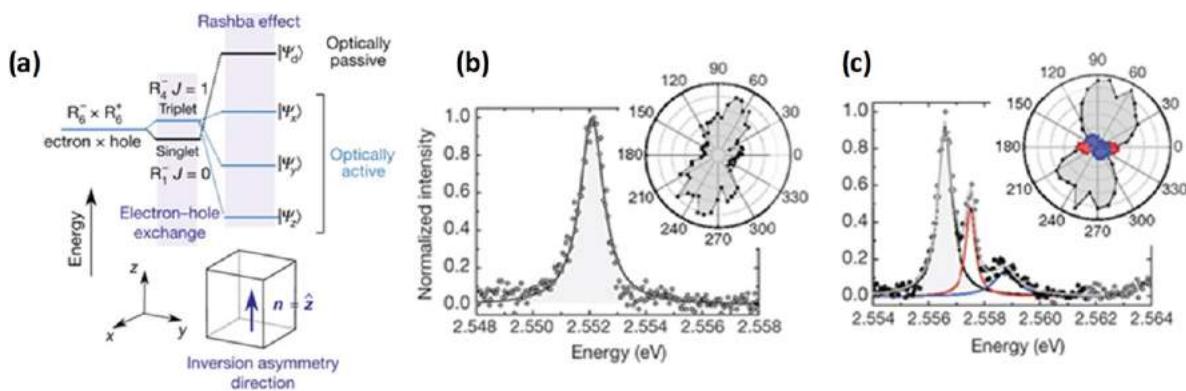


Figure 97. (a) Fine structure of the band-edge exciton considering short-range electron–hole exchange (middle) and then including the Rashba effect (right) under orthorhombic symmetry. The latter splits the exciton into three bright states with transition dipoles oriented along the orthorhombic symmetry axes (labeled x , y , and z) and a higher-energy dark state (labeled “d”). The energetic order of the three lowest sublevels is determined by the orthorhombic distortion. Photoluminescence spectra from individual NCs showing (b) one and (c) three photoluminescence peaks. Adapted with permission from ref 147. Copyright 2018 Macmillan Publishers Limited, part of Springer Nature. All rights reserved.

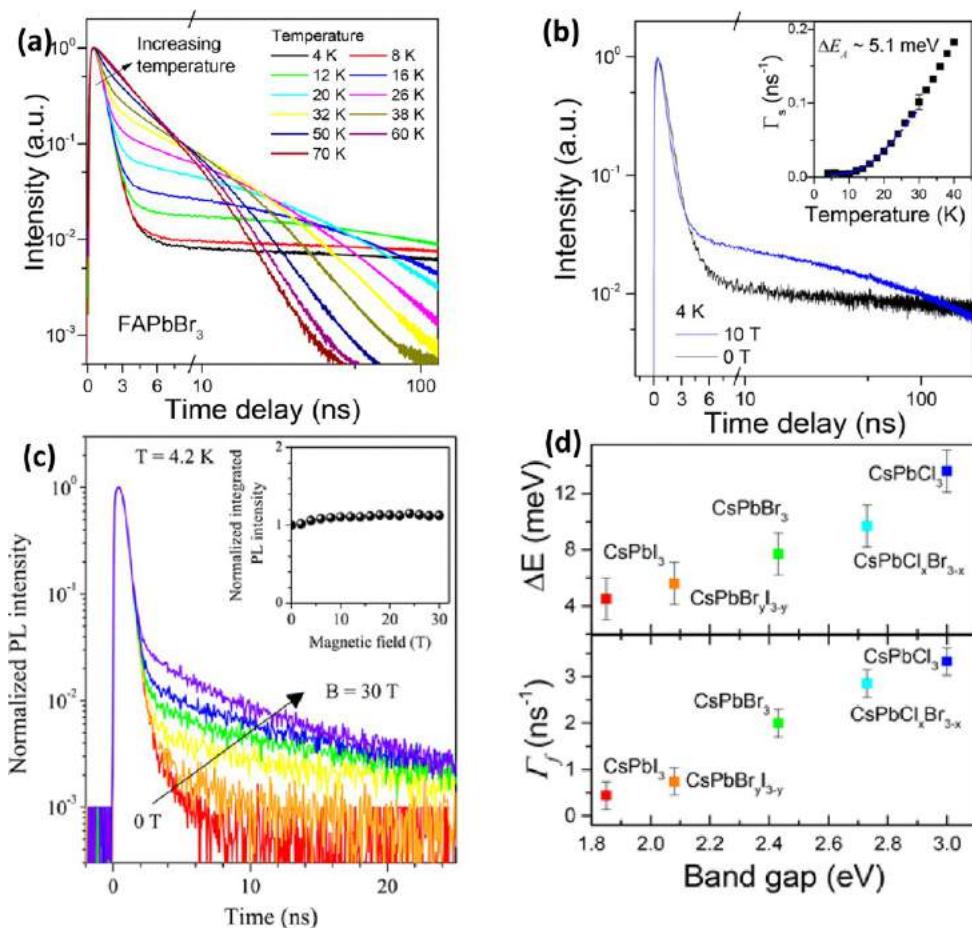


Figure 98. (a) Temperature-dependent PL decay traces in FAPbBr₃ NCs. (b) PL decay curves recorded from FAPbBr₃ nanocrystals at 4 K with and without an applied external magnetic field of 10 T. Inset shows the temperature-dependent relaxation rate of the slow decay component analyzed with the three-level model yielding a bright dark energy splitting of 5.1 meV. Adapted from ref 815. Copyright 2018 American Chemical Society. (c) PL decay recorded at cryogenic temperature for CsPbBr₃ nanocrystals at varying magnetic fields. The inset shows the integrated PL intensity with respect to magnetic field. Adapted from ref 760. Copyright 2017 American Chemical Society. (d) Anion composition dependence of the bright–dark energy splitting (ΔE) and the decay rate of the fast component (Γ_f). The values are plotted vs the band gaps of different nanocrystals at room temperature. Adapted from refs 760 and 815. Copyright 2017 and 2018 American Chemical Society.

states known as exciton fine structure.^{803,805–808} In almost all bulk III–V semiconductors heterostructures, II–VI core–shell

colloidal nanostructures, the lowest available exciton states are found to be optically inactive, also known as dark

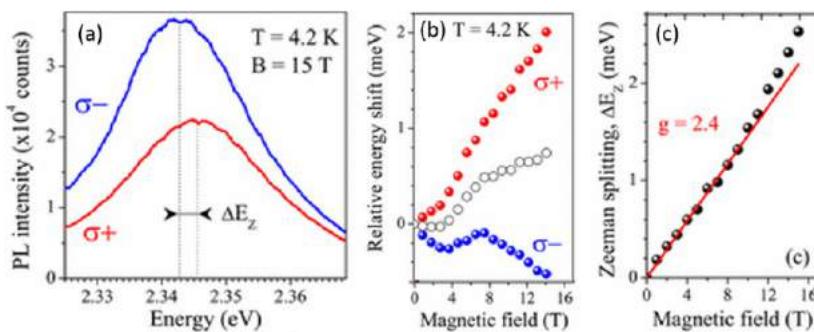


Figure 99. (a) Time-integrated polarization-resolved PL spectra of CsPbBr_3 NCs at $B = 15$ T and $T = 4.2$ K. The spectra are split by the Zeeman splitting, ΔE_z . (b) Magnetic field dependence of the relative spectral positions of σ^- (open blue circles) and σ^+ (red circles) components. Open circles show the shift of the center of gravity of the two polarized components, corresponding to the exciton shift without contribution of the Zeeman splitting. (c) Zeeman splitting of emission line. Red line is a linear fit with $|g| = 2.4$. Adapted from ref 760. Copyright 2017 American Chemical Society.

exciton.^{809–811} In the case of bulk semiconductor the splitting between the bright (optically active) and the dark (optically inactive) exciton is very small, generally less than the thermal energy even at cryogenic temperature. Hence, the photoluminescence decay is not strongly affected by temperature.^{802,803} Nevertheless, the energy separation between them is increased up to tens of meV in the case of semiconductor nanostructures where the photoluminescence decay is prolonged at low temperature due to acoustic phonon-mediated relaxation of the bright exciton to the dark exciton states.^{809,811–813}

In almost all MHPs, it is observed that the photoluminescence decay becomes faster at low temperature where the photoluminescence quantum yield still remains high.^{147,814} The explanation of the high radiative recombination in Pb^{2+} -halide perovskites at low temperature was proposed by Becker *et al.*¹⁴⁷ They claimed the lowest exciton state as the bright triplet state for CsPbX_3 ($X = \text{Br}, \text{Cl}, \text{I}$) crystals structure arising due to combination of strong spin–orbit coupling with Rashba effect.⁸⁰⁶ According to them,¹⁴⁷ if only short-range electron–hole exchange interaction is taken into account then the singlet state lies below the triplet state, making the lowest available exciton state dark (Figure 97a). They showed that inclusion of Rashba effect leads to the alteration of the bright and dark exciton levels in CsPbX_3 NCs. If the effective Rashba field is parallel to one of the orthorhombic symmetry axes of the CsPbX_3 NCs the bright triplet exciton states split into three linearly polarized sublevels (Figure 97b,c).¹⁴⁷ In a detailed study by Sercel *et al.* they demonstrated that the ground state of the perovskite nanostructure is indeed optically inactive (dark) like any other classical semiconductor quantum dots, if only exchange interaction has been considered.⁸⁰⁶ However, the experimentally observed bright exciton level order in tetragonal CsPbBr_3 NCs can be explained including the contribution of the Rashba effect, which supports the theory by Becker *et al.*¹⁴⁷ Moreover, it was shown that the bright–dark state positions could be reversed in low dimensional nanostructures, which, consequently, possess a dark exciton ground state.⁸⁰⁶ Opposite experimental observations were found in the case of CsPbBr_3 , FAPbBr_3 , and FAPbI_3 NCs.^{760,815,816}

Figure 98a shows the temperature-dependent PL decay in FAPbBr_3 NCs. At 4 K, PL decay is biexponential with a dominant fast decay component, followed by a slow component. With rise in temperature the slow components

grows gradually and becomes more prominent at higher temperature. Similar observation was also noticed in the case of CsPbX_3 NCs.^{760,815,817} The first component is assigned to the radiative decay of the bright exciton whereas the slow component is assigned to the dark exciton decay, the rate of which is increases at higher temperature, as shown in the inset of Figure 98b.⁸¹⁵ The lengthening of the dark exciton relaxation rate at higher temperature is due to thermal activation.^{760,815} Figure 98b also shows that, under the application of an external magnetic field of 10 T, the amplitude of the slow decay component enhances which is due to dark exciton states mixing with the bright exciton states resulting into the brightening of the dark excitons.^{760,811,815} Similar observation was also noticed by Cannesson *et al.*⁷⁶⁰ in CsPbBr_3 NCs, as shown in Figure 98c, where, with increase in magnetic field, the amplitude of the slow component enhances due to magnetic field-induced brightening of the dark exciton states. Using a three-level model for bright and dark excitons, Chen *et al.*⁸¹⁵ determined the energy splitting (ΔE) between the bright and dark exciton states, as depicted in Figure 98d. ΔE increases while going from CsPbI_3 to CsPbCl_3 . It depends not only on anion composition but also on A-site cation composition.⁸¹⁵ It has been also demonstrated that an external dopant like Mn^{2+} is able to manipulate the dark and bright exciton mixing.⁸¹⁷ In the case of CsPbCl_3 NCs, a similar brightening of the dark exciton states has been observed upon Mn^{2+} doping.⁸¹⁷ The amplitude of the slow decay component at the cryogenic temperature was enhanced 5–10 times in Mn^{2+} CsPbCl_3 NCs as compared to the undoped CsPbCl_3 NCs.⁸¹⁷

A direct observation of dark exciton emission in FAPbBr_3 NCs has been reported by Tamarat *et al.*⁸¹⁶ Using magneto-optical studies at cryogenic temperature, they observed that a low-energy zero-phonon line appears at 2–2.8 meV below the zero-phonon line of bright triplet state at 7 T, which has been ascribed to dark singlet exciton state resulting due to the mixing of dark states with neighboring bright states. Similar to Chen *et al.*, they also observed magnetic field induced brightening of the dark singlet state at low temperature.⁸¹⁶

At cryogenic temperature, the bright excitons can further split into narrow spectral lines.^{147,818,819} Yin *et al.* had shown in CsPbI_3 NCs the bright exciton split into two linear orthogonal polarized emission with energy separation of few hundred μeV .⁸¹⁹ They also showed that in photocharged CsPbI_3 nanocrystal the doublet emission of bright exciton switched to a single emission peak due to elimination of electron–hole

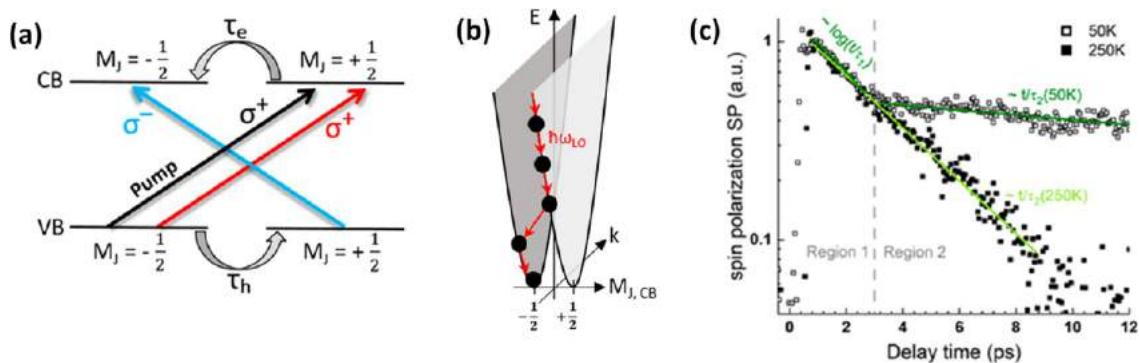


Figure 100. (a) Spin-dependent optical transitions between valence and conduction band states induced by circularly polarized pump and probe beams with similar and opposite helicities. (b) Electron spin-relaxation process in CB due to LO-phonon scattering process. (c) Temperature-dependent SP in CsPbI₃ NCs. At 50 K, an additional spin-relaxation channel appears due to the exciton spin-flip. Adapted from ref 821. Copyright 2020 American Chemical Society.

exchange interaction.⁸¹⁹ In the case of CsPbBr₃ NCs Fu *et al.* found two different kind of fine structure splitting of bright exciton for orthorhombic and tetragonal phases.⁸¹⁸ Under application of external magnetic field of 15 T Canneson *et al.* observed the bright exciton emission from CsPbBr₃ NCs, to be circularly polarized where the left handed circularly polarized light was more intense compared to right handed circularly polarized light (Figure 99a-b).⁷⁶⁰ With increase in magnetic field the splitting between two opposite circularly polarized light enhances due to increased amount of Zeeman splitting from which they could determine the exciton g factor for CsPbBr₃ NCs to be 2.4 with electron and hole g factors of +2.18 and -0.22, respectively (Figure 99c).⁷⁶⁰

Spin-Polarization of Optically Generated Carriers. The exciton spin that determines the singlet/triplet dark/bright character of the states plays a critical role in controlling the optical transitions in semiconductor NCs. For instance, a spin-flip may cause a transition from an optically active (bright) to a passive (dark) state. Therefore, selective excitation of exciton spin is an effective approach to tune the optical properties of NCs.

Spin dynamics of particular spin states of photoexcited carriers could be studied using helicity-dependent time-resolved differential transmission spectroscopy by employing circularly polarized light for pump and probe.⁸²⁰ The helicity of the circular polarization can be controlled by the rotation of the azimuthal angle of the optical axis of a quarter wave plate ($\lambda/4$) with respect to the linear polarization axis of the pump/probe beam. The detector view conventions for positive helicity: σ^+ = left handed circular polarization; negative helicity: σ^- = right handed circular polarization. Figure 100a schematically illustrates the possible optical transitions induced by the circularly polarized resonant optical pumping at the band gap of Pb²⁺-based MHP. Under σ^+ excitation, the electron flips from the $M_{J,\text{VB}} = -1/2$ state into the $M_{J,\text{CB}} = +1/2$ state because of the conservation of angular momentum in an optical transition. Then, the conduction band electron can undergo an intraband M_J spin-flip from $M_{J,\text{CB}} = +1/2$ to $M_{J,\text{CB}} = -1/2$ at a rate of $1/\tau_e$. Similarly, the holes in the VB can undergo spin-flip from $M_{J,\text{VB}} = -1/2$ to $M_{J,\text{VB}} = +1/2$ at a rate $1/\tau_h$.

Strohmair *et al.* have reported spin-relaxation processes of free charge carriers in CsPbI₃ nanocubes using circularly polarized differential transmission spectroscopy.⁸²¹ They observed that the spin-polarization (SP_{max}) $[(\Delta T/T)_{\sigma+\sigma-}]$

decreases dramatically for above band gap excitation and is almost 70% smaller at 2.32 eV compared to SP_{max} detected at 1.92 eV. The spin-polarization of the photoexcited charge carriers diminishes during thermalization and cooling down to the band-edge by emitting longitudinal optical phonons (Figure 100b). In this context, Strohmair *et al.* emphasized the dominant contribution from LO phonons *via* the Elliott-Yafet spin-relaxation mechanism in the case of free carriers in CsPbI₃ NCs due to strong Fröhlich interaction present in MHPs.⁸²¹ At low temperature the spin-relaxation time increases and an additional fast relaxation channel appears due to excitonic processes becoming prominent. The faster spin-relaxation channel at low temperature occurs *via* Coulomb mediated exchange interaction according to the Bir–Aronov–Pikus (BAP) model (Figure 100c).^{821,822} Spin-dynamics has also been studied in polycrystalline MAPbI₃ thin films using helicity-dependent time-resolved transient absorption spectroscopy. The spin-relaxation times of the photoexcited free charge carriers have been found to be in the range of a few picoseconds, and the spin-depolarization was attributed to the Elliott-Yafet (EY) mechanism.⁸²³ In the case of 2D-layered (C₆H₅C₂H₄NH₃)₂PbI₄, the observed exciton spin-relaxation time was even on the shorter time scales. Due to the fact that the exciton binding energy in 2D-layered perovskites is relatively high (\sim 180 meV), the spin-relaxation mechanism is usually controlled *via* Coulomb exchange interaction and is described by BAP model.⁸²² Using pump–probe Kerr rotation, Belykh *et al.* measured that the charge carrier spin-relaxation in CsPbBr₃ perovskite crystals is in the nanosecond regime.⁴⁶ They assigned the long-lasting spin-relaxation time to hyperfine interaction between localized charge carriers and the nuclei spins. Li *et al.*¹⁵² have observed decrease in spin lifetime with decrease in size CsPbBr₃ and CsPbI₃ QDs. In the case of CsPbI₃ QDs, the spin-relaxation time decreased from 3.2 to 1.9 ps for the QD size reduction from 8.3 to 4.2 nm while it decreased from 1.9 to 1.2 ps for CsPbBr₃ QDs with size decreasing from 7.5 to 3.5 nm. Elliott-Yafet spin-relaxation mechanism was postulated to be absent in the case of CsPbBr₃ QDs where electron–hole exchange interaction, surface scattering, and spin–spin interaction have been held responsible as probable spin-relaxation channel.¹⁵² Furthermore, spin-polarization has also been induced externally in MHPs using chiral ligands or by doping with transition metal ions.^{20,817} For example, Long *et al.* were able to achieve 3% spin-polarized photoluminescence

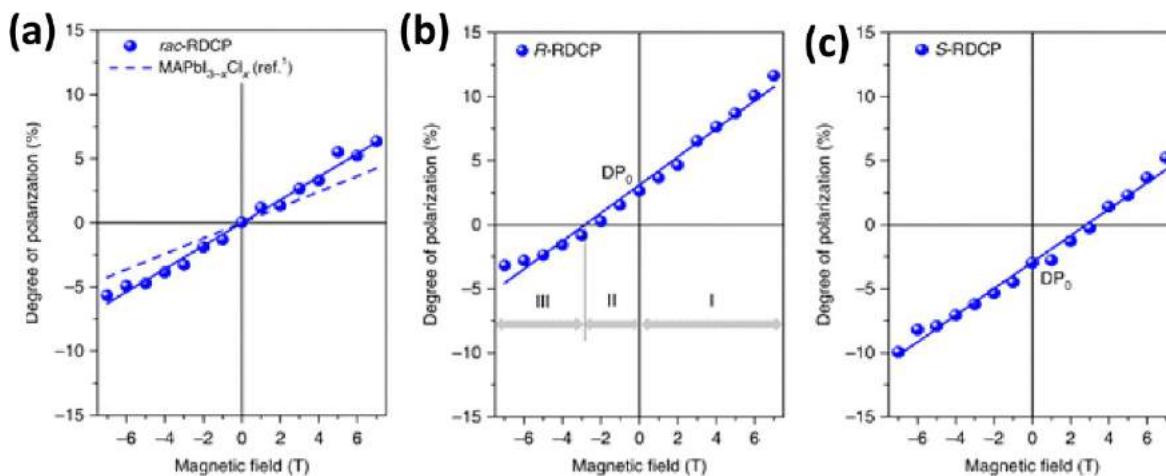


Figure 101. Degree of photoluminescence polarization for *rac*-RDCP (a), R-RDCP (b), and S-RDCP (c) with magnetic field varied from -7 T to 7 T. The graph of R-RDCP is divided into three regions: I, II, and III. At $B = 0$ (no external magnetic field), there is a degree of polarization (DP_0) for R-RDCP. When a positive magnetic field is applied, the degree of polarization increases with the magnetic field (region I). In region II, as a negative magnetic field is applied, the degree of polarization decreases accordingly until it is zero. As a stronger negative magnetic field is applied, the degree of polarization changes sign from positive to negative (region III). Opposite phenomena are observed for S-RDCP. Adapted with permission from ref 20. Copyright 2018 The Authors.

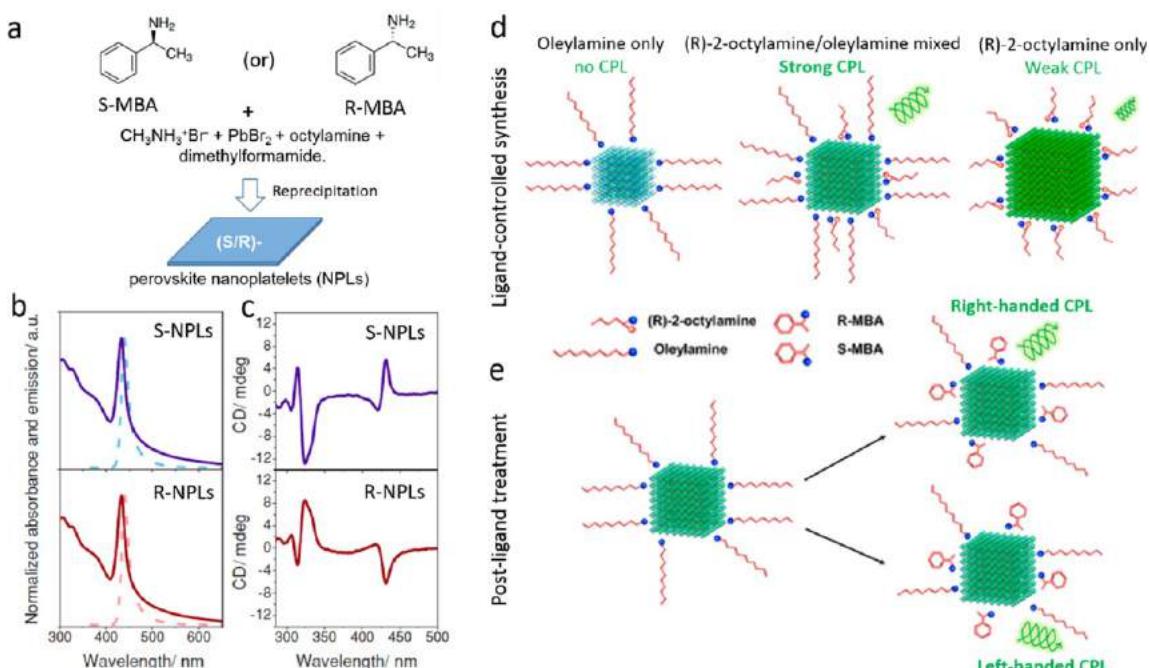


Figure 102. (a) Schematic representation of the synthesis of chiral organic-inorganic hybrid perovskite NPLs by reprecipitation in the presence of chiral ligands (S-MBA and R-MBA). (b,c) UV-vis absorption (solid line) and PL (dotted line) (b), and the corresponding CD spectra (c) of the enantiomeric NPLs obtained with S-MBA and R-MBA ligands. Panels b and c are adapted from ref 829. Copyright 2018 John Wiley & Sons, Inc. (d,e) Schematic illustration of the synthesis of FAPbBr_3 nanocubes in the presence of the chiral ligand (R)-2-octylamine (d) and post-synthetic surface treatment of FAPbBr_3 nanocubes with chiral ligands (R-, S-MBA.Br) (e). Panels d and e are adapted from ref 825. Copyright 2020 American Chemical Society.

from the reduced dimensional chiral perovskites at zero applied magnetic field due to the different emission rates of right and left handed circularly polarized light.²⁰ To achieve the same magnitude of spin-polarized photoluminescence from achiral perovskite an external magnetic field of 5 T is needed, as shown in Figure 101.

Chiral Perovskite NCs. Thanks to the flexible chemical composition and surface chemistry of perovskite NCs, additional functions and properties can easily be introduced through surface modifications. Recently, there has been a

growing research attention regarding the introduction of chiral function into halide perovskites by their interaction with chiral ligands.^{540,824-840} The concept of chirality or handedness refers to the functional property of chiral materials/molecules to not be superimposable with their mirror images, and these are called enantiomers (*i.e.*, (R)-(-) (right) and (S)-(+) (left)).⁸⁴¹ The distinctive property of chiral molecules is their ability to rotate the plane of linearly polarized light differently depending on the respective enantiomer. The reason for this so-called optical rotation lies in the circular birefringence, *i.e.*,

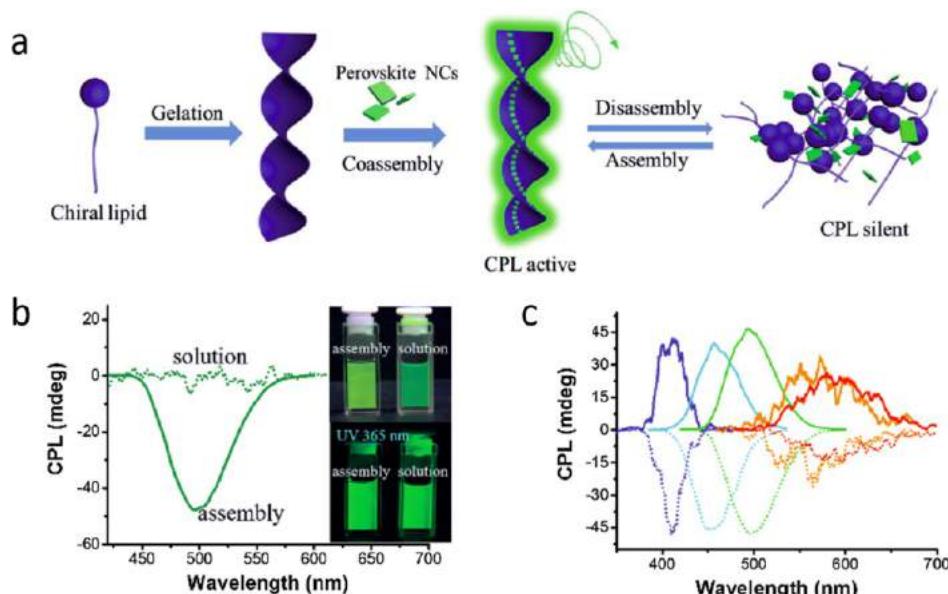


Figure 103. (a) Schematic illustration showing the gelation of chiral lipids into helical structure followed by coassembly of perovskite NCs along the helical gel to obtain chiral assemblies that emit circularly polarized luminescence (CPL). (b) CPL spectra of chiral gel induced CsPbBr_3 assemblies and the disassembled CsPbBr_3 colloidal solution, with the latter obtained by dispersing the gel-perovskite assemblies in chlorobenzene solution. The inset shows the photographs of the colloidal solutions containing perovskite NC assemblies and individual NCs (disassembled) under room light (top) and UV light (bottom, 365 nm) illumination. (c) CPL spectra of chiral gel induced CsPbX_3 NC assemblies of different halide composition. Adapted with permission from ref 830. Copyright 2018 John Wiley & Sons, Inc.

the refractive index is different for right and left circularly polarized light. With linearly polarized light depicted as a superposition of two circularly polarized waves (clockwise and counterclockwise), the polarization of light is rotated when passing through a chiral medium. Chiral molecules play a crucial role in many biological processes, real life systems and electronic devices.⁸⁴² In general, most small chiral molecules exhibit optical activity in the ultraviolet region of the light spectrum. However, interestingly, it has been shown that such molecules can confer chirality on colloidal metallic or semiconductor NCs that show optical activity in the visible to near-IR region by means of surface functionalization. Over the last few decades, a significant amount of research work has been done regarding the fabrication and application of chiral plasmonic, and semiconductor NCs. Recently, these concepts have been extended to recently emerged perovskites for a variety of applications, including ferroelectrics, chiroelectronics, and chiro-spintronics. Readers may also refer to two latest review articles on chiral perovskites.^{840,1356}

The initial studies on chiral perovskites were mainly focused on 1D single crystals, 2D-layered systems and bulk thin films.^{20,824,826,828,832,836,837,839,840} In 2003, Billing *et al.*⁸²⁸ reported the synthesis of organic-inorganic hybrid 1D perovskite single crystals ($((S)\text{-C}_6\text{H}_5\text{C}_2\text{H}_4\text{NH}_3)[\text{PbBr}_3]$) by *in situ* incorporation of a chiral amine (1-phenylethylammonium (PEA), also called methylbenzylammonium (MBA)) as the counterion. However, their chiral properties were not investigated. After being out of limelight for a few years, chiral perovskites have regained attention after the chiroptical study of $(S\text{-MBA})_2\text{PbI}_4$ and $(R\text{-MBA})_2\text{PbI}_4$ 2D-layered perovskite films by Moon and co-workers in 2017.⁸³⁷ These perovskite enantiomers were achieved through the incorporation of the respective chiral organic molecule (*S*-MBA and *R*-MBA) into the layered lead-iodide framework. They exhibit oppositely signed circular dichroism (CD) signals at their excitonic

transitions, while the chiral molecules alone do not show any CD signal at these wavelengths. After these findings, chiral 2D-layered perovskite films and single crystals have been significantly explored regarding their synthesis and applications.^{824-826,832,836,838-840} For instance, Chen *et al.*⁸³⁹ and Wang *et al.*⁸³² independently demonstrated the fabrication of flexible photodetectors using chiral 2D perovskites for efficient detection of circularly polarized light. The principle of these CP light photodetectors is the generation of different photocurrents for different circular polarization states of detected photons. Furthermore, chiral 2D perovskites are being studied for exploring circularly polarized photoluminescence (CPP)^{824,826} and ferroelectricity.⁸⁴⁰ Recently, these concepts have been extended to colloidal perovskite NCs. They can be excellent candidates as CP light sources for optoelectronic applications owing to their high PLQY and easily tunable emission color. However, unlike chiral 2D-layered perovskites, only a few studies have been reported on colloidal chiral perovskite NCs.

Generally, there are three different synthetic approaches to obtain colloidal chiral perovskite NCs: (1) *in situ* incorporation of chiral ligands during the synthesis (Figure 102)^{825,829,834} (similar to the case of chiral 2D-layered perovskites), (2) post-synthetic surface treatment with chiral molecules⁸²⁵ or chiral assemblies (Figures 102 and 103), and (3) synthesis of helical perovskite NCs (not yet achieved). Figure 102b summarizes the first two (*in situ* and post-synthetic) strategies one can use to synthesize chiral perovskite NCs. In this regard, Waldeck and co-workers⁸²⁹ demonstrated the *in situ* incorporation of chiral molecules (*S*-MBA and *R*-MBA) onto hybrid perovskite NPs synthesized by the reprecipitation method (Figure 102a). In this case, the chiral MBA cation molecules were introduced along with achiral octylamine as ligands into the precursor solution. The injection of precursor solution into toluene leads to the formation of chiral hybrid perovskite NPs, which exhibit

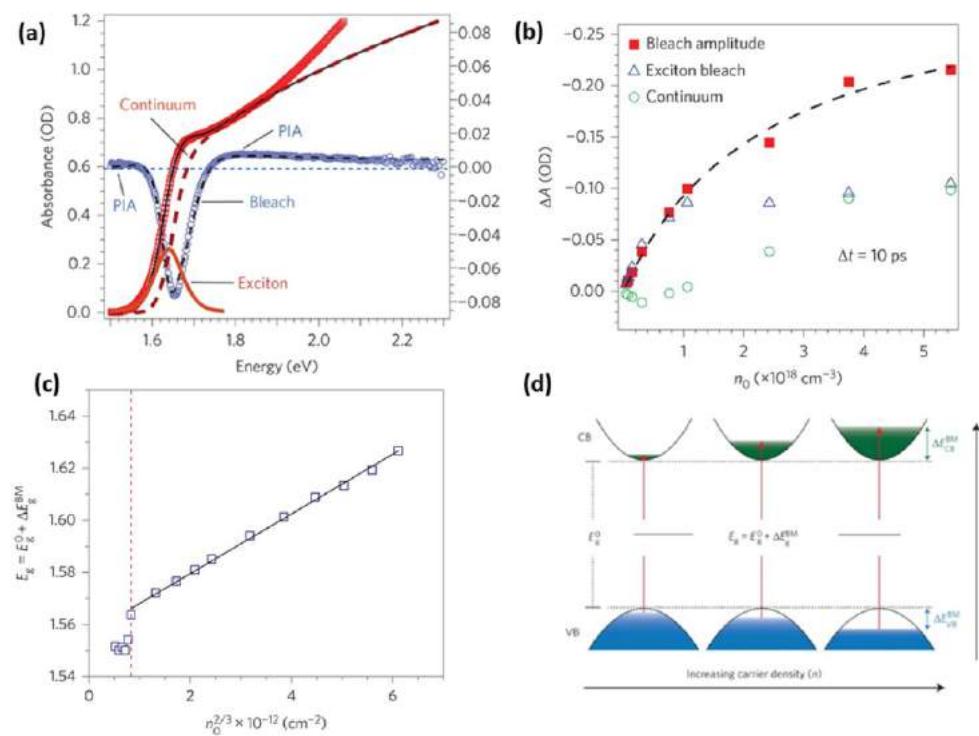


Figure 104. (a) Steady-state (red squares) and transient absorption (TA) (blue circles) spectra of a typical MAPbI₃ perovskite thin film. Black line: modeled band-edge absorption. Red dashed line: continuum contribution. Red line: exciton contribution. Adapted with permission from ref 848. Copyright 2015 Nature Publishing Group. (b) ΔA at $\hbar\omega_{\text{probe}} = 1.65$ eV as a function of the initial charge carrier density n_0 . Blue triangles: exciton contribution. Green circles: continuum band contribution. Adapted with permission from ref 848. Copyright 2015 Nature Publishing Group. (c) Modulation of the intrinsic band gap of MAPbI₃ according to the Burstein–Moss model. The vertical dashed line marks the onset of band gap broadening. The solid line is a linear fit to the data after the onset. The linear trend indicates an agreement with band filling by free charge carriers. Adapted with permission from ref 849. Copyright 2014 Nature Publishing Group. (d) Schematic representation of the Burstein–Moss effect showing the contribution from both, electrons in the conduction band (CB) and holes in the valence band (VB) due to their similar effective masses. Adapted with permission from ref 849. Copyright 2014 Nature Publishing Group.

sharp excitonic absorption and emission features that are consistent with quantum-confined NPs (Figure 102b). The NPs (*S*-*R*-NPs) obtained with the two enantiomer ligands (*S*-*R*-MBA) exhibit a mirror-image like CD spectrum with peaks at their excitonic absorption (Figure 102c), where the ligand molecules alone do not show any CD signal. The authors take this as a clear indication for the ligands imprinting their chirality onto the NPs electronic structure. In addition, the CD peaks observed at higher energy (~ 300 – 350 nm) were assigned to the charge-transfer bands between the chiral ligands and the NPs surface (Figure 102c). Very recently, this *in situ* synthesis of chiral perovskite NCs has been extended to CsPbBr₃⁸³⁴ and FAPbBr₃⁸²⁵ NCs using the short chiral ligand α -octylamine (Figure 102d). The partial replacement of oleylamine with (*R*)-2-octylamine during the synthesis of FAPbBr₃ NCs results in monodisperse chiral perovskite NCs that emit CPL with a luminescence dissymmetry (*g*) factor of 6.8×10^{-2} , which is among the highest of reported perovskite materials.

In addition to these direct synthetic strategies, post-synthetic treatments have also been used to induce chirality in perovskite NCs by two different approaches. Firstly, the surface of presynthesized perovskite NCs can be modified with chiral ligands through ligand exchange (Figure 102d).⁸²⁵ For instance, Luther and co-workers demonstrated the post-synthetic ligand exchange on FAPbBr₃ NCs with chiral ligands (*S*-*R*-MBA), which induces CPL with an average dissymmetry

g-factor of $\pm 1.18 \times 10^{-2}$. The second post-synthetic approach is the supramolecular self-assembly of NCs into helical structures.^{830,843} Previously, this approach was extensively used to induce chirality in plasmonic NCs using biomolecules such as DNA, DNA origami, and supramolecular fibers.^{843–845} Recently, Shi *et al.*⁸³⁰ demonstrated the supramolecular self-assembly of CsPbX₃ (X = Cl, Br, and I) into chiral assemblies that emit CPL by mixing chiral organogels made of lipids (*N,N*'-bis(octadecyl)-L-glutamic diamide (LGAm) and its enantiomer (DGAm)) with perovskite NCs in hexane (Figure 103a). The shape of the emission spectra remains unchanged with a slight red shift after self-assembly. However, interestingly, the perovskite NC assemblies exhibit CPL with a dissymmetry *g*-factor up to 10^{-3} , while disassembled gels do not show CPL (Figure 103b). The disassembled gels were obtained by dissolving the DGAm–CsPbBr₃ hybrid assemblies in chlorobenzene. The wavelength of the CPL peak is easily tunable across the visible spectrum of light by varying the halide composition (Figure 103c). Furthermore, it has been shown that these chiral assemblies could be incorporated into polymer film to obtain flexible CPL devices. Despite these interesting reports, the study of chiral perovskite NCs is still in the beginning stage. There are many questions yet to be addressed regarding colloidal chiral perovskite NCs. For instance, the mechanism of chiral induction *via* surface ligands on 3D perovskite NCs is still unclear. In addition, the number of chiral ligands used so far to modify the surface of perovskite

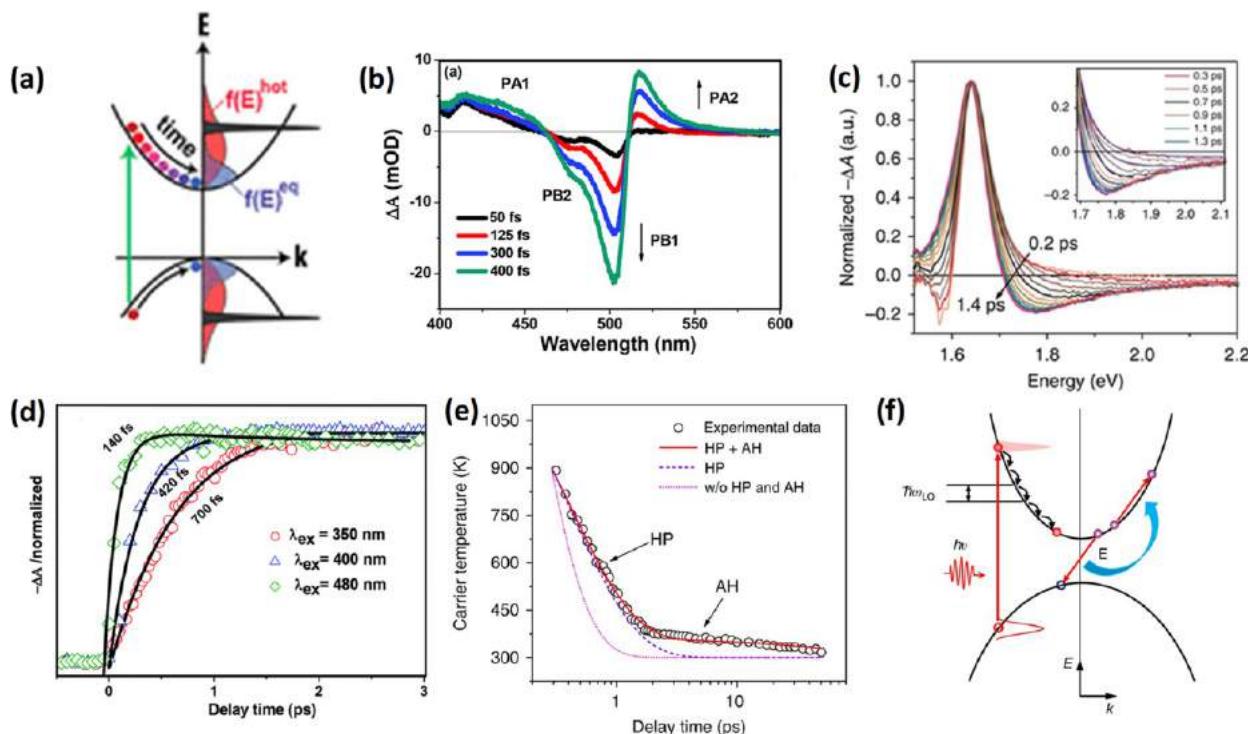


Figure 105. (a) Thermalization and relaxation schemes of the photoexcited electrons and holes. The initial δ -like distribution of the electrons and holes changes to an equilibrium distribution in two stages. Adapted under a Creative Commons CC-BY license from ref 857. Copyright 2018 American Chemical Society. (b) Time-dependent evolution of the TA spectrum ($\lambda_{\text{ex}} = 350$ nm) of CsPbBr_3 NCs in the early time window (0.05–0.4 ps). Adapted with permission from ref 851. Copyright 2017 Royal Society of Chemistry. (c) Normalized TA spectra with variable delays from 0.2 to 1.4 ps, with the inset showing the high-energy tails fitted to the M–B distribution for extraction of the HC temperature. Adapted with permission under a Creative Commons Attribution 4.0 International License from ref 50. Copyright 2017 The Authors. (d) Formation kinetics of the PB1 band (representing HC cooling time) of CsPbBr_3 NCs as a function of the excitation wavelengths. Adapted with permission from ref 851. Copyright 2017 Royal Society of Chemistry. (e) HC cooling dynamics in a MAPbI_3 thin film following photoexcitation at 2.48 eV with a carrier density n_0 of $10.4 \times 10^{18} \text{ cm}^{-3}$ at RT. Black circles: HC temperature extracted from TA spectra. The lines show the calculated HC cooling dynamics for $\tau_h = 0.6$ ps: with a hot-phonon (HP) effect only (violet dashed line); with both HP and Auger heating (AH) effects (bright red line); and without HP and AH effects (magenta line). Adapted with permission under a Creative Commons Attribution 4.0 International license from ref 50. Copyright 2017 The Authors. (f) Schematic of the hot electron relaxation process. Auger heating, which contributes to further deceleration of hot electron cooling, is also shown. The same processes apply to the hot holes but are omitted for clarity. Reprinted with permission under a Creative Commons CC BY 4.0 license from ref 50. Copyright 2017 The Authors.

NCs are limited because many chiral molecules are not soluble in nonpolar solvents. Furthermore, perovskite NCs with helical morphology have yet to be achieved. More importantly, the application of chiral perovskite NCs in optoelectronic and spintronic devices needs to be explored.

Charge Carrier Dynamics. Understanding the fate of the photoexcited charge carriers in a semiconducting material is of fundamental importance for the development of efficient optoelectronic devices. Photoexcitation produces electron-hole pairs whose energy relaxation channels depend on a variety of conditions.^{10,846,847} Followed by initial carrier thermalization, the hot charge carrier loses its energy by emitting optical phonons and successively relaxes down to the electronic band-edge. The charge carriers then either radiatively decay to produce light or recombine nonradiatively. The following sections discuss various such energy relaxation dynamics in MHP under ultrafast photoexcitation.

Figure 104a represents a typical steady state linear absorption spectrum (red squares) and a transient absorption (TA) spectrum (blue circles) of a planar MAPbI_3 perovskite thin film. The absorption spectrum of MAPbI_3 shows a steep rise at the absorption onset (at 1.6 eV). According to the Elliott

model (Figure 90b,c), both excitonic and band to band continuum transitions contribute to the optical band gap in MHPs. This is shown by the representative TA spectrum ($\hbar\omega_{\text{pump}} = 1.82$ eV) at a pump–probe delay of 10 ps. It has two general features: a sharp photobleach (PB) and a broad photoinduced absorption (PIA).⁸⁴⁸ The PB signal peaking at ~1.65 eV has been attributed to both band filling and free carrier induced bleaching of the exciton transition. The PIA has been related to several factors such as hot carrier (HC) cooling, polaron formation and free carrier absorption.⁸⁴⁸ With increase in the excitation fluence, the amplitude of the PB signal ($-\Delta A$) increases in a nonlinear fashion (Figure 104b). The spectral position was found to depend on the initial carrier density n_0 . Manser *et al.* reported a carrier density-dependent blue shift and broadening of the PB signal in MAPbI_3 thin films due to the Burstein–Moss shift (Figure 104c).⁸⁴⁹ When the photogenerated carriers fill the electronic band-edge states (valence and conduction band), the effective band gap shifts toward higher energy due to Pauli blocking (Figure 104d).

Hot Carrier Relaxation Dynamics. When excited by photons with energy higher than the band-gap energy, the charge carriers (electrons and holes) are produced in states

much above the band-edge states with a non-equilibrium distribution in energy. These “hot carriers” thermalize through carrier–carrier scattering processes within 1 ps. The subsequent process is called “carrier cooling”, in which the quasi-equilibrated HCs (at temperature higher than the lattice temperature and governed by the Fermi–Dirac distribution) dissipate their excess energy as heat *via* phonon emission and come to the band-edge states (Figure 105a).^{50,850}

The overall hot carrier cooling process can be probed using ultrafast transient absorption and photoluminescence measurement techniques. Figure 105b shows the TA spectra of CsPbBr₃ NCs for short (0.05–0.4 ps) time scales, where the TA spectra comprise positive differential absorption (ΔA) bands PA1 and PA2 and a strong negative photobleach signal due to carrier-filling effect of the band-edge states.⁸⁵¹ The formation kinetics of this bleach signal (PB1) delivers a carrier cooling time (τ_C).^{851,852} The time dependence of the recovery of the secondary weak bleach signal (PB2) (Figure 105b) matches with the formation kinetics of PB1. The lower energy absorption band (PA2), which is related to the HC cooling, has been recently attributed to polaron formation.^{853–856} Another approach to probing HC cooling is by measuring the carrier temperature by fitting the high-energy tail of the TA spectra to a Maxwell–Boltzmann distribution (Figure 105c).^{50,848} However, the exact estimation of the individual contributions of hot holes and hot electrons to the carrier cooling time is difficult as the excess energy is almost equally distributed between the hot electrons and hot holes. As the energy of HC depends on the energy provided in excess of the band gap energy, τ_C directly correlates with the excitation energy. The higher the excitation energy is, the longer is the hot carrier cooling time. In the case of CsPbBr₃ NCs, Mondal *et al.* reported an increase in τ_C from 140 to 700 fs, as the excitation wavelength was changed from 480 to 350 nm (Figure 105d).⁸⁵¹

The HC cooling dynamics also depends on the excitation fluence and cannot be explained by the hot phonon effect alone.^{706,850,858} For all APbBr₃ NCs (A = Cs, MA, and FA), HC cooling slows down with an increase in excitation fluence.⁸⁵⁹ At high excitation fluence, the carrier–carrier interactions come into the picture due to high carrier densities and this can cause re-excitation of the hot charge carriers (called “Auger heating”) and slow down the overall HC cooling process. Fu *et al.* reported that, at carrier densities above 10^{19} cm⁻³, the HC cooling dynamics is governed by the combined effect of a hot phonon and Auger heating.⁵⁰ Figure 105e shows the HC cooling dynamics in MAPbI₃ when photoexcited at 2.48 eV at room temperature with an initial carrier density of 1×10^{19} cm⁻³. Two gradients are clearly visible, indicating the presence of two distinct HC cooling mechanisms which are the hot phonon effect and the Auger effect. There are two distinct types of Auger recombination processes: the intraband and the interband Auger recombination among which the latter process (also called Auger heating) causes a nonradiative transfer of the electron–hole recombination energy to a third electron (or hole), resulting in the excitation of the third carrier to higher energy level (Figure 105f). As the Auger lifetime (τ_{Aug}) is dependent on the volume (V) of the NCs ($\tau_{Aug} \sim V^{1/2}$), the HC cooling time at high excitation fluence is expected to be dependent on the NCs’ volume.⁸⁶⁰ Indeed, an increase in the HC cooling time from 12 to 27 ps has been observed with increasing the size of the NCs from 4.9 to 11.6 nm.⁸⁵⁰

In CsPbX₃ (X = Br and I) NCs, τ_C (for the same amount of excess energy) decreases while going from iodide-based NCs to bromide-based NCs: CsPbI₃ (580 fs) > CsPb(Br/I)₃ (380 fs) > CsPbBr₃ (310 fs).⁸⁵² As the halide’s orbitals mainly contribute to the valence band of the NCs, this HC cooling time seems to represent the effective hot hole cooling dynamics rather than the hot electron cooling.⁸⁵² The HC cooling time is also influenced by the A-site cation composition in MHP NCs, where it was observed that τ_C decreases from Cs- to FA-based NCs: CsPbBr₃ (390 fs) > MAPbBr₃ (270 ps) > FAPbBr₃ (210 fs).⁸⁵⁹ A faster τ_C in hybrid perovskites (FAPbBr₃ and MAPbBr₃) compared to that in the Cs-based MHP is attributed to a stronger carrier–phonon coupling facilitated by the vibrational modes of the organic cations.^{859,861,862} The role of molecular vibrations in HC relaxation is confirmed by the ability to slow down the cooling process at lower temperatures for FAPbBr₃, while no/a less strong effect is observed for CsPbBr₃ NCs.⁸⁶³ The dependence of the HC cooling on the B-site cation was studied by a partial replacement (60%) of Pb with Sn and found to slow down the HC cooling time of MAPbI₃ from 0.3 to 93 ps.⁸⁶⁴ A very slow HC cooling in FASnI₃ thin films was reported to give rise to hot PL.⁸⁶⁵ However, as an opposite trend (a faster HC cooling dynamics upon partial Sn substitution in CsPbBr₃ NCs) is also reported recently,⁵²⁸ and more studies are needed to understand the exact role of “Sn” on HC cooling dynamics in Sn-doped lead-halide perovskite NCs.

In quantum-confined systems, the HC cooling time depends on the size of the NCs. For example, HC cooling dynamics become faster (from 700 to 500 fs) when the size of MAPbBr₃ NCs is increased from ~ 4.9 to 11.3 nm.⁸⁵⁰ A slower HC cooling in smaller NCs is attributed to the intrinsic phonon bottleneck effect due to the availability of fewer phonon modes.^{850,866} Interestingly, a small change in HC cooling time of CsPbBr₃ NCs on varying the edge length from 2.6 to 6.2 nm indicates the absence of any hot phonon bottleneck in this class of NCs.⁸⁶⁷ The effect of dimensionality on HC cooling dynamics was also investigated. The HC cooling was reported to be much faster in 2D MAPbI₃ NPs compared to quasi-3D system⁸⁵⁷ due to the low dielectric screening and high surface to volume ratio of the 2D NPs. An increase in HC cooling time from 260 to 720 fs for A₂PbI₄ on changing the organic spacers from C₆H₅C₂H₄NH₃⁺ ($\epsilon = 3.3$) to HOC₂H₄NH₃⁺ ($\epsilon = 37$) is a reflection of the influence of dielectric screening on HC cooling dynamics, too.⁸⁶⁸ A slowdown of HC cooling due to the formation of large polarons at low excitation fluence has also been reported very recently.^{853,869,20}

Carrier Trapping and Recombination Dynamics in MHPs. Radiative recombination of the charge carriers is one of the most important channels in direct band gap semiconductors that determines their utility in optoelectronic devices. Radiative recombination is slow compared to exciton dephasing, spin-relaxation, and HC cooling time and is commonly observed on the picosecond–nanosecond time scale. If indeed the perovskites were perfectly defect tolerant,^{21,870} the radiative recombination would have been the only route for the relaxation of the charge carriers. However, multiexponential PL decay dynamics of most perovskites NCs even at low excitation fluence suggests the existence of sub-band-gap energy levels arising from various defects that act as trap centres.^{101,871–876} These trapped carriers can return to the conduction or valence band and

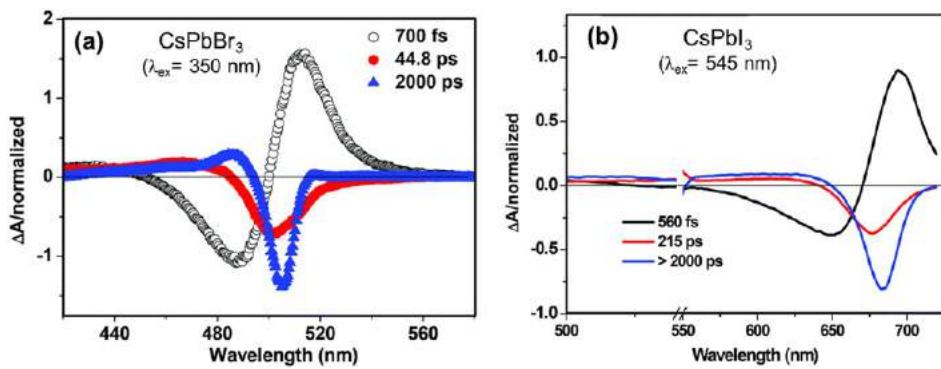


Figure 106. Decay-associated TA spectra of (a) CsPbBr_3 and (b) CsPbI_3 NCs. Adapted with permission from ref 851. Copyright 2017 Royal Society of Chemistry.

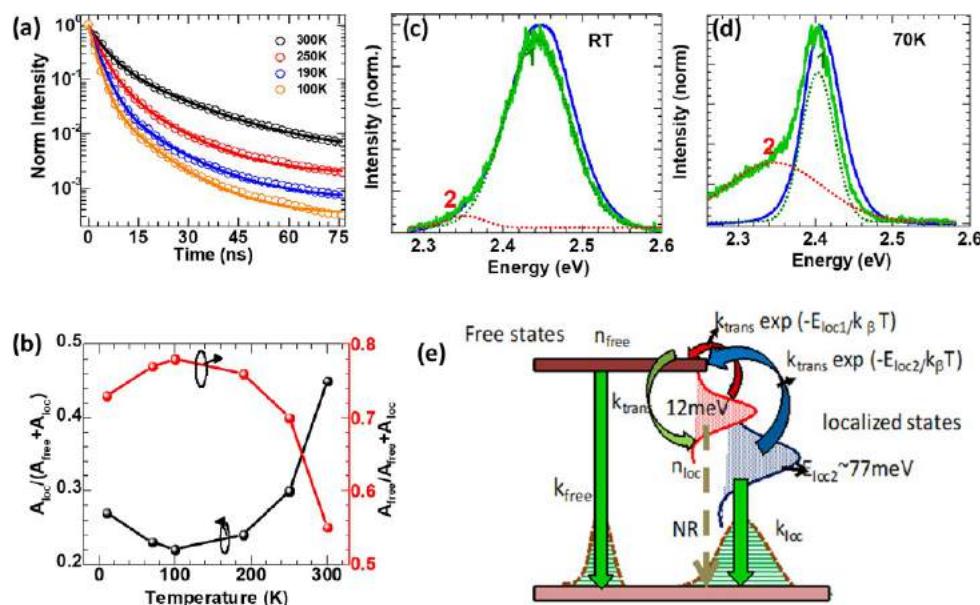


Figure 107. (a) Temperature-dependent PL decay in CsPbBr_3 NCs. (b) Relative weight contributions of the free vs localized states in controlling the PL dynamics at different temperatures. Time-resolved PL spectra (PL1 at $t = 0$ and PL2 at $t = 32$ ns) at room temperature (c) and at low temperature (d) for CsPbBr_3 NCs. (e) Schematic of the model depicting interactions between free and localized states. Adapted with permission from ref 814. Copyright 2018 John Wiley & Sons, Inc.

recombine radiatively, if the de-trapping process is effective such as in the case of shallow defects.^{875,814} This process is responsible for an additional longer decay component in the PL decay profile.^{877,878} However, when the separation between the trap state and band-edge is large, as in the case of deep traps, the charge carriers relax nonradiatively.⁸⁷⁵ For smaller NCs, which have a high surface to volume ratio, “surface trapping” can also facilitate nonradiative recombination of the charge carriers resulting in lowering of the PL efficiency and acceleration of the PL decay dynamics.

While the time constants for the radiative processes are most commonly estimated from the PL decay profiles measured using the time correlated single-photon counting (TCSPC) technique, the nonradiative recombination processes are much faster and require ultrafast TA and PL measurements. Most often, the temporal profile of the photobleach recovery signal (in TA measurements) contains a fast component due to carrier trapping in addition to the long component due to radiative recombination. The bleach recovery kinetics of CsPbBr_3 NCs consists of two components (~ 45 ps and ~ 2

ns) (Figure 106) in which the former has been assigned to electron trapping.⁸⁵¹

In the case of CsPbI_3 , carrier trapping time is estimated as $\sim 215\text{--}400$ ps.^{175,851,879} A recent theoretical study shows that halide vacancies in the NCs are the major contributor to the defect energy levels, which are shallow in nature for CsPbBr_3 and CsPbI_3 , but deep in the case of CsPbCl_3 .^{86,194} The high trap density in large band gap CsPbCl_3 NCs accounts for its weak luminescence (PLQY $< 10\%$) and TA studies show multiple carrier trapping channels with time constants ranging from 3 to 64 ps.^{148,783,880,881,782} Dey *et al.* have studied the temperature-dependent time-resolved PL dynamics in the case of CsPbBr_3 NCs, where they observed the PL decay getting faster when lowering the temperature.⁸¹⁴ Additionally, a low-energy PL peak appeared at low temperature for the long time delays (Figure 107a-d). Both effects can be attributed to the presence of defect states. While at room temperature the efficient detrapping process slows down the PL decay, the emission from these localized states becomes significant at low temperatures as evident in the formation of the additional low-energy PL peak (Figure 107e).⁸¹⁴ Very recently, trapping of

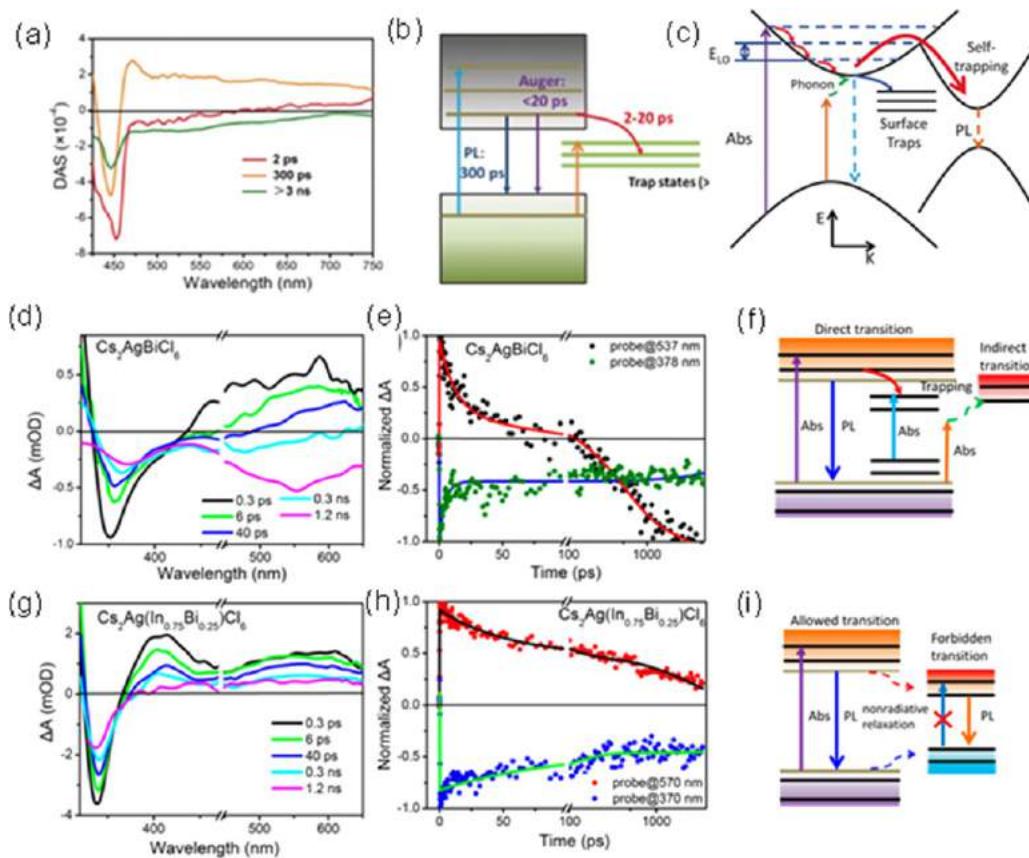


Figure 108. (a) Decay-associated spectra of $\text{Cs}_3\text{Bi}_2\text{X}_9$ NCs. (b) Model illustrating several photoinduced processes in $\text{Cs}_3\text{Bi}_2\text{X}_9$ NCs. Adapted with permission from ref 543. Copyright 2017 John Wiley & Sons. (c) Schematic illustration of the carrier dynamics of the $\text{Cs}_2\text{AgSb}_{0.25}\text{Bi}_{0.75}\text{Br}_6$ double perovskites. Adapted with permission from ref 571. Copyright 2019 John Wiley & Sons. Respective transient absorption spectra, kinetics, and schematic model explain the carrier relaxation channels of (d–f) $\text{Cs}_2\text{AgBiCl}_6$ and (g–i) $\text{Cs}_2\text{AgIn}_{0.75}\text{Bi}_{0.25}\text{Cl}_6$ NCs. Adapted from ref 884. Copyright 2018 American Chemical Society.

the hot charge carriers in states within the band itself has been reported for APbBr_3 NCs.^{189,882,883}

Lead-free perovskite NCs, which are recently receiving increasing attention due to their nontoxic nature,^{543,544,571,884} possess a very low PLQY and are so far less explored. For $\text{Cs}_3\text{Bi}_2\text{X}_9$ ($\text{X} = \text{Cl}, \text{Br}, \text{I}$) NCs, the estimated time constant for carrier trapping, band-edge radiative recombination and trapped charge carrier relaxation are 2–20 ps, ~300 ps and >3 ns, respectively (Figure 108a,b).⁵⁴³ Bleach recovery kinetics of $\text{Cs}_2\text{AgSb}_{0.25}\text{Bi}_{0.75}\text{Br}_6$ NCs reveal three components which have been attributed to self-trapping of the charge carriers (1–2 ps), surface trapping (50–100 ps), and geminate recombination (>5 ns).⁵⁷¹ TA spectra of $\text{Cs}_2\text{AgBiCl}_6$ and $\text{Cs}_2\text{AgIn}_{0.75}\text{Bi}_{0.25}\text{Cl}_6$ show two-component ground-state bleach recovery with time constants of ~100 ps due to carrier trapping and >2 ns due to radiative recombination.⁸⁸⁴ In the former case, the trapping contribution is, however, larger and an additional strong bleach signal due to sub-band-gap trap state absorption or indirect band gap transition is observed (Figure 108d). Recently, in the case of $\text{Cs}_2\text{AgBiBr}_6$ NCs, Dey *et al.* showed that the PL originates from defect-related bound excitons at the Γ -point corresponding to the direct band transition, *via* trapping of holes occurring on a time scale of hundreds femtoseconds.⁷⁷⁹ The PL measurements on the picosecond time scale using a streak camera revealed that the PL maximum, which is originally close to the excitonic resonance, shifts by more than 1 eV toward longer wavelength/

lower energy within tens of picoseconds. This has been attributed to intervalley scattering. Whereas the emission from the direct bound excitons decays fast, the indirect emission showed a slow recombination.⁷⁷⁹ More experimental studies in combination with theoretical calculations are needed for a clear understanding of the underlying photophysical processes in these systems. Readers interested in carrier dynamics of lead-free perovskites may go through the accounts of Yang and Han.⁸⁸⁵

Exciton Recombination. In bulk and NC LHPs, both excitons and free carriers contribute to the radiative recombination.⁸⁴⁹ The populations of excitons and free carriers are determined by the initial exciton concentration and the exciton binding energy (E_B). Excitons in bulk LHPs possess a very small E_B , but the η_{PL} is typically lower than 10%.⁸⁸⁶ On the other hand, the quantum and dielectric confinement effects in LHP NCs increase E_B and the η_{PL} can approach unity at relatively low excitation density. At higher exciton concentrations, the Auger recombination pathway, including biexcitons and trions,^{887–889} and trap-assisted nonradiative recombination⁸⁸⁵ come into play. Therefore, it is obvious that the suppression of nonradiative recombination losses is essential to realize the optoelectronic applications of LHPs.

It has been suggested that 2D LHPs possess a very high E_B that results in a low nonradiative recombination rate. This is due to (i) a relatively low density of intrinsic defects (owing to high defect formation energy), (ii) the presence of distinct

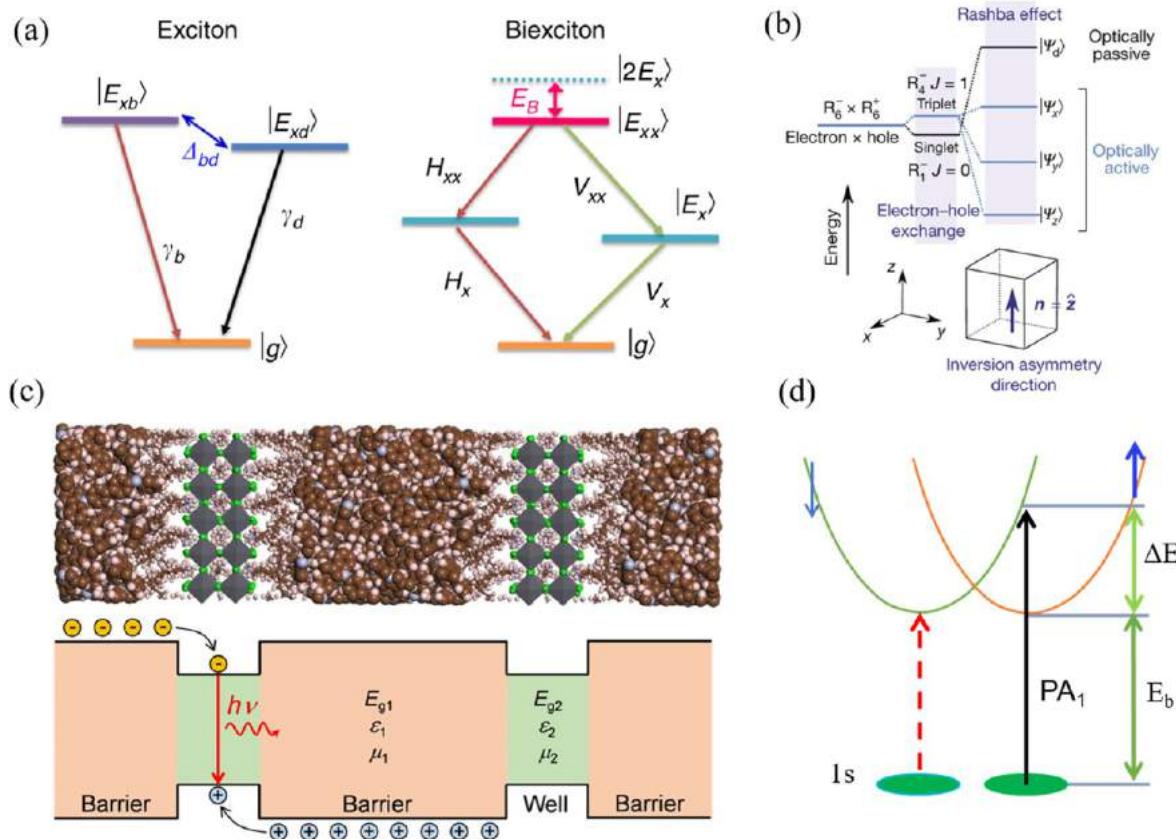


Figure 109. Excitonic characteristics in the lead-halide perovskites. (a) Schematic illustration of charge carrier recombination, including exciton and biexciton transitions, in the 2D CsPbBr_3 perovskites. Adapted with permission under a Creative Commons CC BY license from ref 891. Copyright 2019 The Authors. (b) Schematic band structure demonstrating short-range electron–hole exchange and Rashba effect in 3D orthorhombic CsPbBr_3 NCs. Adapted with permission from ref 147. Copyright 2018 Macmillan Publishers Limited, part of Springer Nature. All rights reserved. (c) Schematic (bottom) and molecular model (top) of the dielectric quantum wells formed between low dielectric constant, k , (barriers) and 2D MAPbBr_3 perovskites (wells), illustrating excitonic recombination to enhance E_B in the wells. Adapted from ref 211. Copyright 2016 American Chemical Society. (d) Schematic band diagram depicting Rashba splitting in that occur due to SOC in the 2D $(\text{C}_6\text{H}_5\text{C}_2\text{H}_4\text{NH}_3)_2\text{PbI}_4$.

polaronic effects, and (iii) the Rashba splitting induced bright triplet excitons (Figure 109a,b).^{147,890,891} More specifically, a high carrier recombination rate can be achieved by increasing the overlap between hole and electron wave functions by quantum confinement, enhancing the exciton localization (the Frenkel-like excitons).^{892,893} In fact, higher exciton binding energy should lead to high biexciton binding energy and thus recombination probability. Biexciton states are manifested by many-body excitonic interactions where two bright exciton states of opposite spins (± 1) comprise one biexciton state. They have very low optical transition probability and are not stable at room temperature. Thus, they could exist either at cryogenic temperatures or under femtosecond pulse laser excitation. Chen *et al.* showed that the coupling of CsPbBr_3 NPs (where exciton binding energy is very high) with plasmonic nanogap leads to an enhancement in the biexciton recombination under continuous wave excitation at room temperature.⁸⁹¹ As shown in Figure 109a, a biexciton state decays through a cascade process of emitting either two horizontally or vertically polarized photons. The biexciton emission energy ($\hbar\omega_{xx}$) is determined by the energy gap between the biexciton energy (E_{xx}) and single exciton emission (E_x) via $\hbar\omega_{xx} = E_{xx} - E_x$. Thus, when two bright excitons bind together to form one biexciton, the energy of the whole system is decreased by Δ_{xx} ($=2\hbar\omega_x - \hbar\omega_{xx}$), which is the biexciton

binding energy. Indeed, the enhancement of E_B plays a crucial role in high-performance light-emitting devices. E_B can be increased by more than 1 order of magnitude from ~ 10 meV in 3D bulk LHPs^{894–896} to > 150 meV in 2D LHPs^{200,892,895,897,898} due to dielectric confinement effect (Figure 109c).^{895,899,900} In the quasi-2D perovskites, $(\text{BA})_2(\text{MA})_{n-1}\text{Pb}_n\text{I}_{3n+1}$, one can increase E_B up to 470 meV.⁹⁰¹

Strong spin–orbit coupling and inversion asymmetry have been observed in inorganic CsPbX_3 LHP NCs.¹⁴⁷ It has been proposed that these systems also exhibit a high degree of Rashba splitting in the excited-state energy levels, which alters the degeneracy of triplet excited states and the order of energy sublevels, thereby yielding a bright triplet state as the lowest energy state.¹⁴⁷ This is distinct from most quantum emitters, including organic fluorophores and inorganic quantum dots, in which the lowest excited states correspond to the dark triplets.¹⁴⁷ It is noteworthy that recent experimental observations have suggested that the Rashba splitting effect becomes more pronounced in 2D quantum well and quasi-2D LHPs (Figure 109d).⁹⁰²

Multiexciton Dynamics. When the excess energy available to a HC is high enough, it can generate a second exciton by transferring this energy. Generation of multiple excitons by absorption of a single photon can enhance the PCE of single-junction photovoltaics. In bulk semiconductors, the carrier

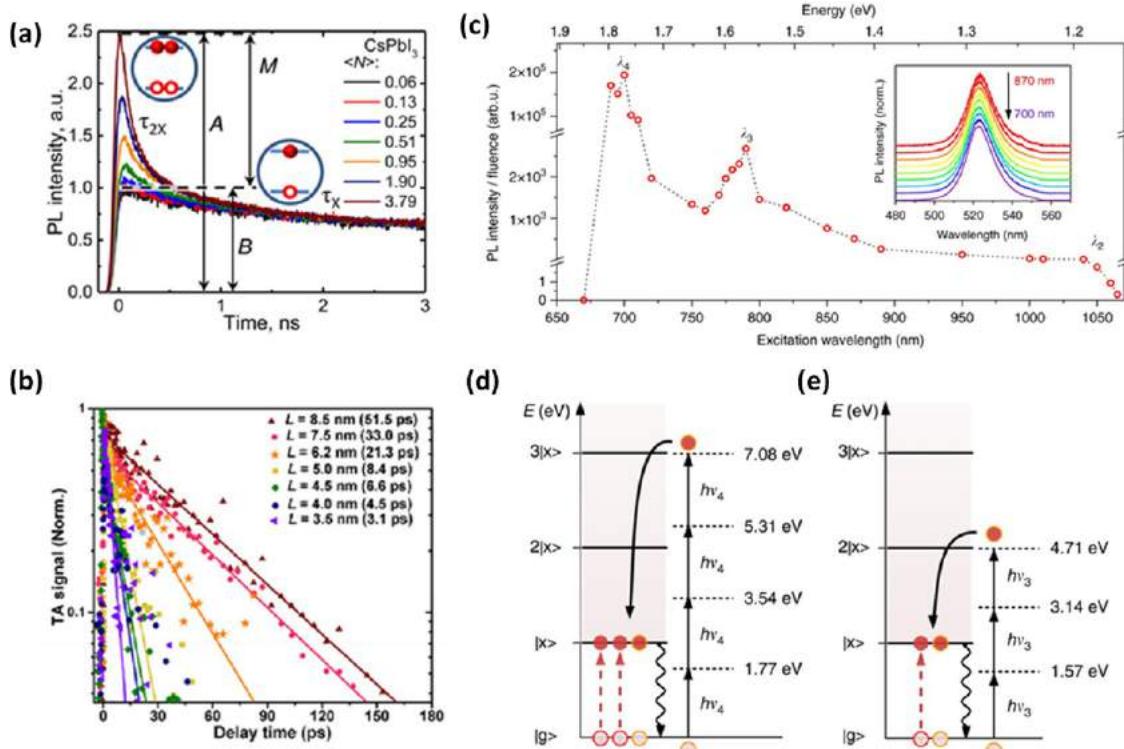


Figure 110. (a) Pump-fluence-dependent PL dynamics of CsPbI_3 . At early time, a short-lived PL component due to biexcitons (denoted as τ_{2X}) emerges at higher pump intensities. A and B denote the amplitudes of the total PL signal and its single-exciton component, respectively, while M = A-B denotes the amplitude of the multiexciton signal. Adapted from ref 854. Copyright 2016 American Chemical Society. (b) Variation in biexciton lifetime with varying sizes of CsPbBr_3 NCs. Adapted with permission from ref 907. Copyright 2018 Tsinghua University Press and Springer-Verlag GmbH Germany, part of Springer Nature. (c) Nonlinear absorption-induced PL in CsPbBr_3 NCs as a function of the below-band-gap excitation wavelength. The dashed line is a guide for the eye. The inset shows the normalized PL spectra for excitation wavelengths varying from 870 to 700 nm. Energy diagram of the resonances between multiphoton excitation and multiexciton generation in CsPbBr_3 NCs. Photoexcitation at $3E_x$ (d) and $2E_x$ (e) and subsequent generation of three (d) and two (e) excitons *via* multiple photon excitation processes with photons of energies $h\nu_4$ and $h\nu_3$, respectively. Panels c–e are adapted with permission under a Creative Commons CC by license from ref 908. Copyright 2018 The Authors.

multiplication efficiency is usually low due to rapid intraband relaxation processes. However, in the nanoscale regime, multiexciton generation is more efficient with a minimal energy loss. For example, generation of seven excitons is documented for PbSe QDs upon excitation with a photon energy of $7.8E_g$ indicating an energy loss of only $\sim 10\%$.⁹⁰³ Multiexcitons can also be generated using high fluence of the excitation laser pulse. Even though the solar flux density is not high enough to produce multiple excitons, studies on multiexciton dynamics are commonly performed using high photon flux.^{854,872,904–906} However, as the multiexciton dynamics is independent of the method of generation, the results of these studies can be applied to improve solar cell applications. Makarov *et al.* studied multiexciton dynamics in CsPbI_3 NCs by monitoring the PL kinetics as a function of the pump fluence.⁸⁵⁴ The appearance of an additional fast decay component at higher laser fluences (Figure 110a) indicates the formation of multiexcitons. The generation of a large number of charge carriers in spatially confined NCs enhances the carrier–carrier interaction, which leads to Auger recombination, an additional nonradiative channel for the relaxation of the charge carriers. As both VB and the CB edge states of the perovskite NCs can accommodate a maximum of two charge carriers (two-fold degeneracy), multiexciton generation in these systems is limited to biexcitons.⁸⁵⁴ As the carrier–carrier

interaction is enhanced in a confined condition, the volume (V) of the NCs influences the biexciton lifetime of a system.

Systematic studies of the volume dependence of the Auger lifetime of a series of NCs (FAPbBr_3 and CsPbBr_3) with varying sizes from a strongly regime to a weakly confined regime, confirm the decrease in the biexciton lifetime with decrease in NC volume (Figure 110b).^{863,907} The volume scaling of the biexciton lifetime (τ_{xx}) is usually represented as $\tau_{xx} = \gamma V$, where γ is the scaling factor, whose value is found to be an order of magnitude lower for FAPbBr_3 ($0.068 \pm 0.005 \text{ ps/nm}^3$) and CsPbBr_3 ($0.085 \pm 0.001 \text{ ps/nm}^3$) compared to CdSe or PbSe QDs (for which $\gamma \approx 1 \text{ ps/nm}^3$).⁸⁶³ However, the reason for this large variation is not yet clear. A high multiexciton efficiency and low multiexciton generation threshold are advantageous from the practical point of view, and in this context, intermediate-confined FAPbI_3 NCs appear to be the best choice. Multiexciton generation with a threshold of $2.25E_g$ and an efficiency of 75% has been demonstrated for this system.⁹⁰⁹ Even for CsPbI_3 , a carrier multiplication efficiency of 98% is reported for $E_{\text{exc}} \geq 2E_g$.⁹¹⁰ The biexciton lifetime of the pure CsPbX_3 NCs varies with the halide composition as CsPbI_3 (90–115 ps) > CsPbBr_3 (40–74 ps) > CsPbCl_3 (~ 20 ps).^{854,855,860,888,904,911,912} Systems with higher biexciton lifetime are of great interest as they provide a longer period for the extraction of biexcitons prior to nonradiative Auger recombination. Mondal *et al.* have shown that the

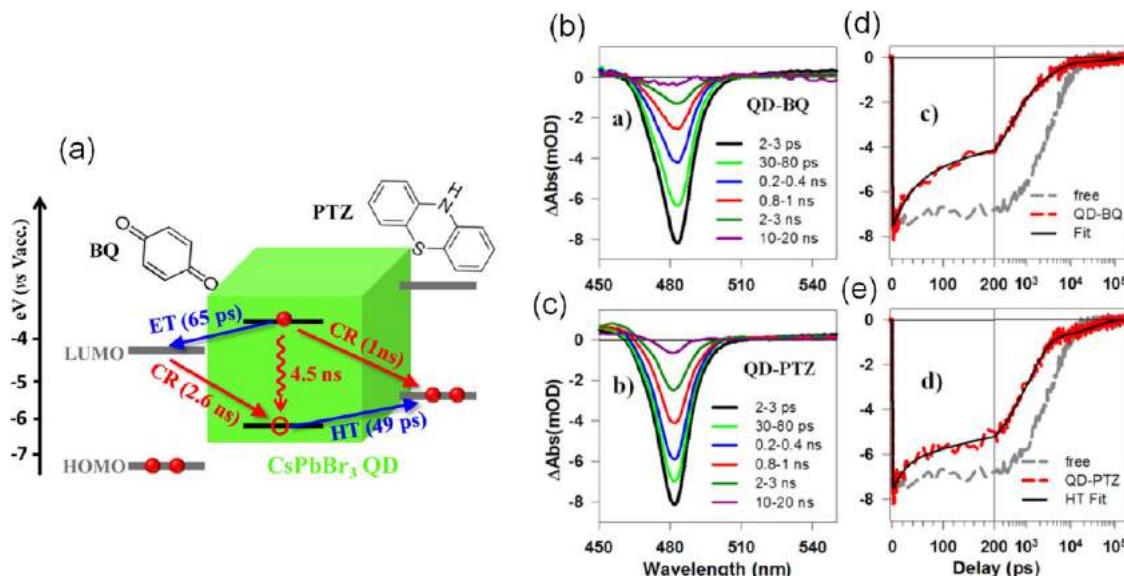


Figure 111. (a) Schematic energy level diagram of CsPbBr_3 NCs-BQ/PTZ complexes and possible charge separation and recombination channels. (b,c) TA spectra NCs-BQ and NCs-PTZ complexes at indicated time delays after 400 nm excitation. (d,e) Corresponding accelerated bleach recovery kinetics as compared with the free NCs (gray dashed line). Reproduced from ref 921. Copyright 2015 American Chemical Society.

biexciton lifetime of CsPbI_3 can be almost doubled by doping a small amount of chloride or formamidinium ion into the system.⁹¹² Eperon *et al.* found a longer biexciton lifetime (198–227 ps) in hybrid perovskite NCs, FAPbBr_3 and MAPbI_3 , compared to all-inorganic, CsPbBr_3 NCs (74 ps).⁸⁸⁸ The effect of dimensionality of the perovskite NCs on the biexciton lifetime has also been studied using CsPbBr_3 NPs and NRs of different lateral areas and rod lengths, respectively.⁹¹³ A linear correlation is found between the biexciton Auger lifetime and the NP lateral area and the NR length, which is related to exciton collision frequency. Reduced Auger probability per collision in 2D materials (NPs) explains the longer biexciton lifetime of it compared to that in 1D NRs.

Another possible nonradiative loss channel is the formation of a trion, which is a localized center containing three charged particles. A positively charged trion consists of two holes and one electron and a negatively charged one comprises two electrons and a hole. These species are formed on photo-excitation of a NC, which already contains a trapped electron or hole. Since the formation of trions requires re-excitation of the same NC, it can be avoided by performing the measurements under vigorously stirring, such that each photon is absorbed by a fresh NC sample. As the trions influence the PL behavior of the NCs (e.g., contributed to PL intermittency), it is important to understand the trion dynamics and several studies have been dedicated to this.^{26,914,915} A trion lifetime of 235 ps has been estimated by comparing the normalized bleach/PL kinetics of static and stirred CsPbI_3 colloidal NCs.⁸⁵⁴ Yarita *et al.* estimated the lifetime of a biexciton and a trion in CsPbBr_3 NCs to be 39 and 190 ps, respectively, by performing pump-fluence-dependent TA measurements.⁹¹⁶ Wang *et al.* determined a trion lifetime of 220 ± 50 ps for CsPbBr_3 NCs through carrier doping using double pump–probe spectroscopy.⁹¹⁷ In another study, negative trions were generated in FAPbBr_3 NCs using strong hole acceptors like CuSCN and their lifetime was estimated (~ 600 ps).⁹¹⁸ Considering that the trions are generally formed due to surface trapping of an electron or a hole, post-synthetic surface

treatments can suppress the trion recombination process.^{882,919} Additional information on this topic can be found in a recent review.⁹²⁰

Nonradiative multiexciton annihilation processes can be avoided by below band gap multiphoton excitation and generation processes.⁹⁰⁸ Manzi *et al.* observed the PL centered at 523 nm from CsPbBr_3 NCs assembly for a wide range of below band gap nonlinear excitations (Figure 110c).⁹⁰⁸ They noticed that the spectral shape of the emitted PL remained unchanged while the emission intensity highly depended on the excitation wavelength. PL can be observed starting at an excitation wavelength around $\lambda_2 = 1030$ nm (photon energy $h\nu_2 = 1.20$ eV $\simeq 0.50E_g$). The PL intensity then increases toward lower excitation energies in a nonmonotonic fashion. Two distinct peaks, located at an excitation wavelength of $\lambda_3 = 790$ nm and $\lambda_4 = 700$ nm (corresponding to the photon energies $h\nu_3 = 1.57$ eV $\simeq 0.66E_g$ and $h\nu_4 = 1.77$ eV $\simeq 0.75E_g$, respectively), have been found with the PL intensity being several orders of magnitude higher (10^3 and 10^5 , respectively) than the signal detected in the vicinity of λ_2 . These particular energies (at λ_3 and λ_4) perfectly match the multiples of the exciton energy $h\nu_x$, suggesting a multiple photon absorption and a subsequent resonant generation of multiple excitons. A schematic representation of the combined multi photon excitation and multiexciton generation processes in CsPbBr_3 NCs system is shown in Figure 110d,e. For the excitation wavelength λ_4 , the NCs assembly undergoes a 4-photon absorption and reaches an energy level resonant with $3E_x = 7.10$ eV. Likewise, for the excitation wavelength λ_3 , a 3-photon absorption process occurred, giving rise to photogenerated excitons with an energy resonant with $2E_x = 4.73$ eV.

Charge Transfer Dynamics. Our discussion so far has been restricted to different intrinsic relaxation processes of the photogenerated charge carriers in perovskites. However, for applications like in solar cells, these photoactive materials are sandwiched between carrier harvesters. It is thus necessary to have an understanding of how charge-transfer dynamics (at the donor–acceptor interface) competes with the dynamics of

intrasytem relaxation processes. In this section, we highlight some of the charge-transfer studies on various perovskite NCs with a variety of carrier acceptors.

Single Electron/Hole Transfer. Wu *et al.* investigated the electron and hole-transfer dynamics from CsPbBr_3 NCs to traditional electron and hole acceptors, benzoquinone (BQ) and phenothiazine (PTZ), respectively (Figure 111a), by monitoring the bleach recovery kinetics of the NCs in presence and absence of the acceptors in ultrafast TA measurements.⁹²¹ The bleach recovery kinetics of the CsPbBr_3 NCs is accelerated in the presence of BQ/PTZ due to charge transfer from the perovskites (Figure 111b–e). Subsequently, several molecular acceptors such as fullerene, ferrocene, tetracyanoethylene, anthraquinones, 1-aminopyrene, etc. were used with a variety of perovskites.^{912,922–931} The time constants for charge transfer between different pairs are summarized in Table 2.

Table 2. Charge Transfer Dynamics between Various Pairs of Perovskite NCs and Molecular Acceptors Investigated through Transient Absorption Measurements (Unless Otherwise Mentioned)

system	carrier acceptor	carrier-transfer time (ps)	ref
electron transfer			
CsPbBr_3	benzoquinone	65 ± 5 (half-life)	921
	benzoquinone ^a	20–50	932
	Rhodamine-B	600	917
	anthraquinone	30	923
	C_{60}	190	923
CsPbI_3	Rhodamine-B	40.6–872	933
	C_{60}	18–45	912
hole transfer			
CsPbBr_3	phenothiazine	49 ± 6 (half-life)	921
	phenothiazine ^a	137–166	932
	4,5-dibromofluorescein	1–1.25	930
	1-aminopyrene	~ 120	927
	TIPS-Pc ^b	~ 5	929
	4-mercaptophenol	$\sim 14.1 \pm 3$	934
$\text{CsPbCl}_x\text{Br}_{3-x}$	tetracene carboxylic acid	7.6 ± 0.2	935
CsPbI_3	1-aminopyrene	~ 170	927

^aThrough terahertz (THz) measurements. ^bTriisopropylsilyl ethynyl pentacene carboxylic acid.

The electronic coupling of the QD and acceptor orbitals influences both charge separation and charge recombination dynamics.⁹³³ It is shown that ~99% photogenerated electrons can be transferred from CsPbI_3 NCs to TiO_2 , with a size-dependent rate ranging from 1.30×10^{10} to $2.10 \times 10^{10} \text{ s}^{-1}$.⁸⁷⁹ Scheidt *et al.* investigated electron transfer between CsPbBr_3 NCs and several metal oxides such as TiO_2 , SnO_2 , and ZnO .⁹³⁶ Formation of a long-lived (~microseconds to milliseconds) species is observed in CsPbBr_3 /methyl viologen²⁺ system.⁹³⁷ A long-lived ($5.1 \pm 0.3 \mu\text{s}$) charge-separated state for $\text{CsPbCl}_x\text{Br}_{3-x}$ perovskite–tetracene complex is also reported.⁹³⁵ Electron and hole transfer from CsPbBr_3 nanoplates to BQ and PTZ with a time constant of 10–25 ps and a half-life time >100 ns of the charge-separated state in NPLs–PTZ is also reported.⁹³⁸ To examine the dependence of the charge-transfer dynamics on the morphology of the perovskite NCs, Ahmed *et al.* studied electron transfer between tetracyanoethylene and the nanospheres, -plates, and -cubes of MAPbBr_3 .⁹²⁴ Electron transfer from photoexcited CsPbBr_3

NCs to CdSe QDs and hole transfer from photoexcited CdSe to perovskites were studied.⁹³⁹ Charge transfer between CsPbBr_3 NCs and CdSe QDs and NPLs is also examined.⁹⁴⁰ The electron transfer from CsPbBr_3 to 2D NPLs is found to be faster as compared to the QDs due to larger surface area and greater density of states in 2D materials. There are also a few studies on charge-transfer dynamics between photoexcited non-perovskite semiconductors and perovskite NCs.^{941–943} Yao *et al.* studied the charge transfer and exciton diffusion process in bilayer and blend structures of $\text{CsPbBr}_3/\text{PCBM}$ interfaces.⁹⁴⁴ By varying the thickness of the CsPbBr_3 NC film on top of the PCBM layer in the bilayer heterostructure, they determined an exciton diffusion length of 290 ± 28 nm for CsPbBr_3 assembly. They concluded that the diffusion process in such cases is followed by an ultrafast exciton dissociation (within 200 fs) at the $\text{CsPbBr}_3/\text{PCBM}$ interface. Even an overall faster charge-transfer process was observed by them in the blend structures which revealed an effective charge extraction from the active layer resulting in a high photo-sensitivity.⁹⁴⁴

Triplet Energy Transfer. As the band-edge excitonic states of the perovskites possess both singlet and triplet characters,⁹⁴⁵ recent studies focused as well on harvesting the triplet exciton. The triplet exciton can be used for sensitization of molecular triplets that generates possibilities like room-temperature phosphorescence, triplet–triplet annihilation mediated photon upconversion, etc.^{46,147,946–951} Several polyaromatic hydrocarbons with appropriate band alignment have been investigated in this regard.⁹⁵² It is interesting to note the enhancement of triplet energy transfer (TET) efficiency with a decrease in NC size. For strongly quantum-confined (edge length of ~ 3.5 nm) CsPbBr_3 NCs, the TET efficiency is found to be as high as $\sim 99\%$, but for 11.2 nm sized NCs, no TET is observed.⁹⁵² This is because for quantum-confined NCs, the electron and hole wave functions spread beyond the NCs surface that enhances the orbital overlap between surface-adsorbed triplet acceptors and the NCs. While direct observation of the formation of molecular triplets confirms TET, a recent study suggests that the mechanism can vary from system to system.⁹⁵³

Multiexciton Extraction. Extraction of multiexcitons prior to Auger recombination is an important process, which can push up PCE of the solar cells by manifolds. While extensive studies on harvesting multiexcitons from the metal chalcogenide quantum dots have been made,^{954,955} there are only a few similar studies with the perovskite NCs. Wu and co-workers demonstrated tetracene-assisted dissociation of up to 5.6 excitons per NC from $\text{CsPbCl}_x\text{Br}_{3-x}$ NCs.⁹³⁵ Multiexciton extraction from $\text{CsPbI}_{3-y}\text{Cl}_y$ using C_{60} has also been successfully achieved.⁹¹² In a recent study, it was shown that out of 14 excitons generated under high excitation fluence in CsPbBr_3 NCs, approximately five electrons get transferred to surface-bound anthraquinones.⁹²⁶ As discussed earlier, Manzi *et al.* showed efficient multiexciton generation also takes place for below band gap excitation in the case of CsPbBr_3 NCs.⁹⁰⁸ While this topic holds promises for further advancements, clearly it is in the early stages of development.

Hot Carrier Transfer. Extraction of hot charge carriers is a challenging task due to their rapid relaxation to the band-edge states. Only a few reports of HC extraction from perovskites are so far available.^{850,932,934,956–958} In an early work, transfer of hot electron and hot hole from CsPbBr_3 NCs to BQ and PTZ was established by monitoring the photoinduced change

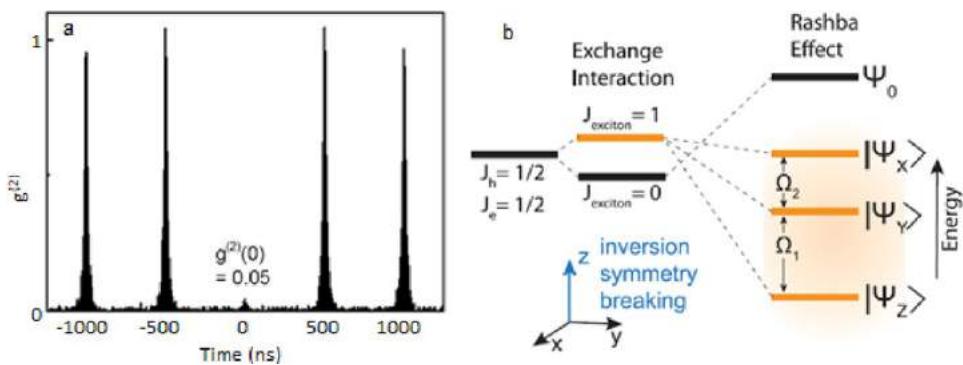


Figure 112. (a) Photon coincidence histogram of a CsPbI_3 MHP QD under pulsed excitation. The low value of coincidence (0.05) at time zero represents single-photon emission. Reproduced from ref 26. Copyright 2015 American Chemical Society. (b) Splitting of exciton fine structure in a MHP QD after the breaking of the inversion symmetry of a CsPbBr_3 QD owing to the Rashba effect, where J_e and J_h are the total angular momentum of electron and hole, Ψ_0 is optically inactive singlet state, and $|\Psi_{x,y,z}\rangle$ are emissive triplet states. Reproduced with permission from ref 24. Copyright 2019 American Association for the Advancement of Science.

in conductivity in time-resolved THz transmission.⁹³² Li *et al.*⁸⁵⁰ showed transfer of hot electrons from MAPbBr_3 to 4,7-diphenyl-1,10-phenanthroline (Bphen) from the sharp drop in bleach amplitude at early time in the presence of the latter. The hot electron extraction efficiency is estimated to be $\sim 83\%$ for ~ 0.6 eV excess energy, and this efficiency progressively decreases with lowering of the excess energy. Hot hole extraction from MAPbI_3 to spiro-OMeTAD has also been demonstrated.⁹⁵⁷ More studies on this important but challenging task are needed.

Summary and Outlook for Optical Properties and Charge Carrier Dynamics. In conclusion, we have tried to review the fundamental optical properties in MHPs covering a broad range of topics. Though still, the stability of MHP NCs is a major issue which needs further improvement from their chemistry point of view for their future commercialization, it is also absolutely necessary to have understanding of their fundamental optical properties for their ultimate employment in the optoelectronic devices. One of the major ongoing debates in the field of MHP nanostructures is to understand the exciton fine structures which governs the radiative *versus* nonradiative rates significantly and it is essential for their light-emitting applications. Though initially it was believed that the lowest exciton state is bright in the case of MHP NCs, in later investigations, it is found to be opposite in many cases. As the transition metal ion doping in MHPs is a quickly emerging topic, it demands more in-depth understanding of the crystal field-induced splitting of bright *versus* dark excitonic states. Hence, a significant amount of research needs to be done in this direction. In addition to the lead-based MHPs, many lead-free MHPs such as double perovskites, 0D MHPs, are emerging as potential semiconducting material for white light generation from self-trapped excitons. The self-trapped exciton formation process in such materials is still not understood. The self-trapping process is highly nonlinear and strongly related with electron–phonon coupling.⁸⁰⁹ Hence, a considerable amount of research should be performed in this direction to understand the phonon dynamics in such material systems to unravel small polaron formations kinetics and the relevant photophysics of these systems. Hot carrier cooling in MHPs is also not fully understood where many theories like large polaron formation,⁹⁵⁹ acoustic to optical phonon up-conversion⁹⁶⁰ have been proposed so far. Recently it is shown by atomistic simulation that lattice vibrations is

important in understanding the hot carrier cooling process in the case of MHPs.⁹⁶¹ Thus, it is also crucial to understand the role of electron–phonon coupling for hot carrier’s extraction at the MHP/organic interfaces for the realization of hot carrier solar cells. Therefore, further research needs to be carried out in this direction. Multiexcitonic processes such as multi photon generation processes are important to increase power conversion efficiencies of solar cells by harvesting below band gap photons and to minimize above band gap excitation induced multiexcitonic annihilation processes such as Auger heating. This nonradiative process becomes dominant at high excitation densities and thus plays an important role in the nonradiative process in the case of high current driven LEDs and lasers. To get better understanding of those processes and how they control the efficiency of perovskite LEDs, such processes need to be monitored in detail in operational devices. The recent findings of ultrafast spin-relaxation dynamics in the case of MHP NCs may become beneficial for MHP-based spintronics such as spin LEDs and spin lasers. Chirally functionalized MHP shows room-temperature circular dichroism²⁰ where a detailed understanding of the spin-dependent chirality transfer process in the photoexcited carriers needs more investigations.

OPTICAL STUDIES OF QUANTUM DOTS AND NANO- AND MICROCRYSTALS AT THE SINGLE-PARTICLE LEVEL

Photoluminescence Blinking in MHP Single NCs. MHP NCs show properties similar to the conventional QDs based on cadmium or lead chalcogenides, such as broad absorption of light in the UV–vis–NIR region, size-tunable absorption and emission, and narrow-band, bright photoluminescence. Like conventional QDs, MHP NCs show stochastic fluctuations of PL intensity, also called PL intermittency or blinking. PL blinking varies with size, morphology, and composition of the MHP NCs, the nature and density of defects, intensity and energy of incident light, and the degeneracy of band-edge states. Quantum emitters are further characterized by the emission of a single photon within their PL lifetime. Recent studies show that the band-edge states of MHP NCs become nondegenerate due to the mixing of electron and hole states, exchange interactions of excitons and the Rashba effect.^{24,147} While the highest lying band-edge singlet state in MHP NCs is optically inactive due to inversion

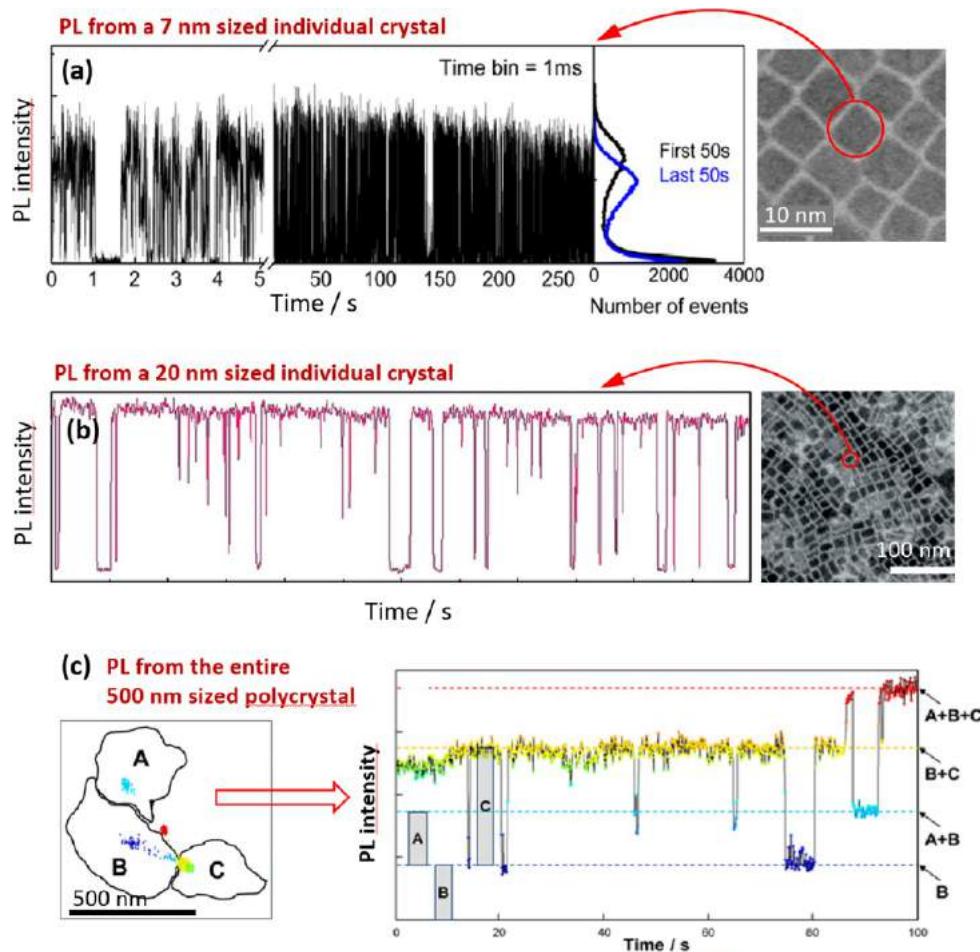


Figure 113. Single-particle PL intensity *vs* time of perovskite crystals with different sizes. (a) CsPbI_3 NCs with a size of 7 nm. Reproduced from ref 26. Copyright 2015 American Chemical Society. (b) MAPbI_3 nanocrystals with a size of 12 nm. Reproduced with permission from ref 962. Copyright 2019 Wiley-VCH Verlag GmbH & Co. KGaA, Weinheim. (c) MAPbI_3 polycrystals with a size of 500 nm, where A, B, and C are three parts of the crystal. Reproduced from ref 963. Copyright 2017 American Chemical Society.

symmetry breaking of perovskite crystals, multiphoton emission from the low lying nondegenerate triplet states can occur.¹⁴⁷ Hence, although single MHP NCs can be spatially isolated and studied, the exclusion of entangled photons from closely spaced band-edge triplet states (Ω_1 and Ω_2 , Figure 112b) becomes necessary. Conversely, excellent antibunching (temporal separation) of photons from single MHP NCs at room temperature suggests that the degeneracy of the band-edge states increases with an increase in temperature, resulting in the maintenance of single-photon emission. Despite the complexity of the band-edge states and entangled photons, which are resolved at temperatures as low as 3.6 K,¹⁴⁷ we focus in this section on the blinking behavior of single MHP NCs by referring to the intrinsic defects or traps, photoionization, and biexciton generation.

The strong quantum-confinement regime in NCs which are smaller than the exciton Bohr radius (<10 nm for MHPs), plays an important role in PL blinking.²⁴ Hence, quantum size effects should be precisely considered during the analysis of single MHP's PL. Differences in the MHP QD blinking behavior when compared to nano- and microcrystals are depicted in Figure 113;^{26,962,963} the multistate blinking of MHP nano- and microcrystals attributed to multiple emissive sites that are governed by metastable nonradiative recombination centers will be discussed in the next section. MHP NCs

show, in addition to the distinct ON and OFF blinking behavior, also intermediate PL levels, similar to GREY states of conventional QDs.⁹⁶⁴

Blinking Mechanism. The ON and OFF periods during QD PL blinking correspond to the neutral and charged states with random switches between the states due to (dis)charging. Like conventional QDs, the blinking of MHP NCs can be assigned to type-A and type-B mechanisms,^{964,965} with random QD charging and discharging the key features of type-A blinking (Figure 114a(i)) and the activation and deactivation of trap or defect states in type-B blinking (Figure 114a(ii)). In type-A blinking, the PL lifetime decreases with a decrease in the PL intensity. ON and OFF time distributions trace the exponential power-law function, $p_{\text{ON/OFF}} \propto t^\alpha \exp(-t/t_c)$, where t_c is the truncation time and α is the power-law coefficient. In contrast, in type-B blinking, the PL lifetime does not change with variations in PL intensity, and the distributions of the ON and OFF times fit with the linear power-law function, $p_{\text{ON/OFF}} \propto t^\alpha$.

Photoactivation of MHP QD surface defects or deep traps can produce a trion. In this scenario, after photoexcitation, a charge is transferred to the crystal shell, leaving behind a net charge with the opposite sign. Upon additional photoexcitation, the core of the QD will then contain three charges (trion state). Subsequently, the excited electron–hole pair will recombine nonradiatively by transferring their excitation

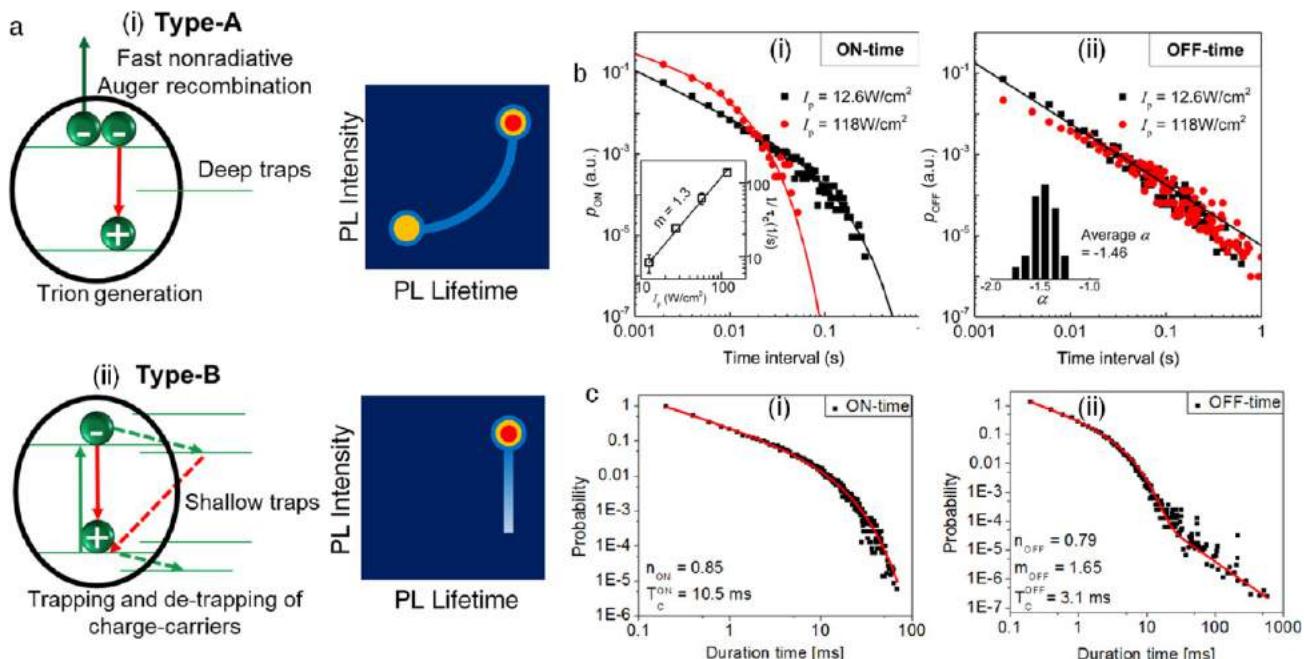


Figure 114. (a) Schemes correlating PL intensity and PL lifetime with the mechanisms of charge carrier dynamics for (i) type-A, (ii) type-B blinking. (b) Power-law functions showing type-A blinking of CsPbI₃ NCs at two excitation pulse intensities. Reproduced from ref 26. Copyright 2015 American Chemical Society. (c) Power-law functions of FAPbBr₃ NCs showing both type-A and type-B blinking. Reproduced from ref 966. Copyright 2018 American Chemical Society.

energy to the extra charge *via* an Auger process instead of emitting a photon. Hence, one observes type-A blinking through repeated nonradiative Auger recombination, charge neutralization and radiative relaxation. For example, Park *et al.* have observed strong photon antibunching and type-A blinking in CsPbI₃ NCs;²⁶ Figure 114b shows the ON and OFF time distributions associated to type-A blinking. Certain MHP NCs show both type-A and type-B blinking in tandem, as was shown for CsPbI₃ QD by Yuan *et al.*⁹⁶⁴ and FAPbBr₃ QD by Trinh *et al.*⁹⁶⁶ For example, the OFF time distribution of FAPbBr₃ NCs follows an exponential behavior initially, which is the characteristic of type-A blinking (Figure 114c(ii)). After the truncation time, a linear behavior is followed, which is characteristic of type-B blinking.⁹⁶⁶ Type-A blinking of these NCs obeys the exponential nature of ON and OFF time distributions. The ON-time duration cutoff for FAPbBr₃ NCs decreases with increasing excitation light intensity and saturates at $\langle N \rangle \approx 1$, whereas the OFF time distribution does not show such behavior. The switching from ON to OFF states takes place through either type-A or type-B pathway. However, MHP NCs turned OFF by ionization continue to be OFF until neutralized.

Trion and multiple exciton states, common to MHP NCs excited with high intensity/energy light, affect the PL quantum efficiency and induce frequent ON/OFF events in the PL trajectories. Like conventional QDs, biexcitons are generated in MHP NCs by mainly two mechanisms, (i) the absorption of two photons with an energy equal or higher than the band gap energy (E_g) or (ii) the absorption of a photon with an energy equal or higher than $2E_g$. The biexciton can emit two photons by first going to the single exciton state and then to the ground state. The second-order correlation function depends on the PLQYs of the biexciton (Q_{XX}) and single exciton (Q_X) states. Under low intensities of excitation, $g^{(2)}(0) \approx \frac{Q_{XX}}{Q_X}$ takes values

close to zero, which is proportional to the ratio of the biexciton (τ_{XX}) and single exciton (τ_X) lifetimes and the ratio (β) of the corresponding radiative rates.^{26,967} Thus, the above equation can be rewritten as $g^{(2)}(0) = \beta \frac{\tau_{XX}}{\tau_X}$. Generally, if the statistics are scaled quadratically with radiative rates and the multiplicity of excitons, the value of β can be 4.

PL intensity transients of NCs show multiple intensity levels, which can be explained by the activation and deactivation of multiple recombination centres (MRC model).^{968,969} Li *et al.* described the relation of PL blinking to MRC and bright biexcitons.⁹⁶⁷ The activation and deactivation of MRCs govern the nonradiative recombination rate in a QD. This rate increases with an increase in the number of activated MRC, and as a result, the PL intensity and lifetime decrease. To account for the changes in PL lifetime and blinking at different intensities of excitation light, Li *et al.*⁹⁶⁷ recorded the single MHP QD behavior at $\langle N \rangle = 0.02, 0.2$, and 2. The PL blinking at $\langle N \rangle = 0.2$ shows more frequent OFF states when compared with the blinking at $\langle N \rangle = 0.02$. The blinking of an MHP QD shows the flickering effect at higher intensities of excitation light, suggesting switching between the bright and dim states. PL blinking at $\langle N \rangle = 2$ is explained based on the activation and deactivation of MRCs and the charging and discharging of the trion state.

Apart from MRC, blinking due to nonradiative Auger recombination is correlated to the particle size. For example, the energy levels of larger MHP NCs are perturbed by the delocalization of the hole state throughout a QD.⁹⁷⁰ An increase in ON-time distribution with an increase in QD size suggests a low trapping rate and high de-trapping rate for larger MHP NCs. These rates can be extracted from the power-law coefficients of ON and OFF time distributions. The trapping and de-trapping rates depend on (i) photoionization of NCs, (ii) charge tunneling from a NC to a trap state, and (iii) the

trapping time of electrons and holes. The nonradiative Auger recombination of trions becomes fast if an MHP NC is photoionized by trapping, which can be analyzed from the OFF time distribution and PL lifetime. The trapping and detrapping time of electrons and holes also affect the recombination rates; nonradiative recombination of the hole in a short-lived trapped state decreases the PL intensity and lifetime.

Blinking Suppression. The blinking behavior of MHP NCs may also depend upon the halide ion and A/B-site cation, halide vacancies, and surface defects.^{882,914,971} For example, with the exchange of bromide to iodide in CsPbBr_3 NCs, Yoshimura *et al.* revealed a considerable increase in the ON time (Figure 115a),⁹⁷² which should be attributed to not only

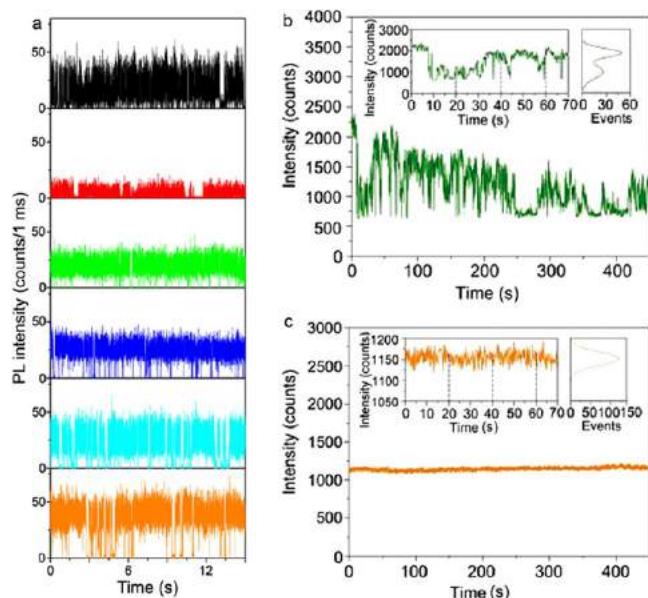


Figure 115. (a) PL intensity transients of a CsPbBr_3 QD as a function of the bromide to iodide exchange reaction before (black), during (red, green, blue, cyan), and after (orange) the addition of PbI_2 dissolved in a mixture of oleic acid and oleylamine. Reproduced from ref 972. Copyright 2020 American Chemical Society. (b,c) PL blinking of CsPbBr_3 MHP NCs (b) without and (c) with a CdS shell. Reproduced with permission under a Creative Commons CC BY 4.0 license from ref 974. Copyright 2019 John Wiley & Sons, Inc.

the exchange of halide ions but also the filling of halide vacancies. These halide vacancy-assisted defects result in Type-A PL blinking, which can be suppressed by filling the vacancies. Chouhan *et al.*⁹⁷³ demonstrated PL blinking suppression in real-time by supplementing MAPbX_3 ($X = \text{Br}, \text{I}$) QDs with MAX. Also, blinking can be suppressed by the passivation of surface defects using shells. For example, Tang *et al.* demonstrated the suppression of the trap-assisted blinking in CsPbBr_3 NCs by the preparation of CdS shells (Figure 115b,c).⁹⁷⁴ Here, blinking suppression is assigned to the passivation of deep electron or hole traps at the interface between the MHP QD core and CdS shell.

Although blinking of MHP NCs with different A-site cations is independently investigated by many groups, systematic single-molecule studies correlating the composition of A-site cation and blinking, are required to understand the role of A-site cation on blinking. Any differences in the blinking behavior

due to differences in the composition at the A-site should be correlated with the dipole moment. Organic cations such as methylammonium (MA^+) and formamidinium (FA^+) ions are dipolar, whereas Cs^+ is unipolar. When compared with Cs^+ and FA^+ , the higher dipole moment of MA^+ and its rapid motion within the lattice create a polaronic screening of the charge carriers. As a result, the exciton–exciton interactions are suppressed in MAPbX_3 . MA^+ is also more susceptible to the fluctuations in the external charge and local current than Cs^+ and FA^+ . Thus, the energy states in MAPbX_3 or CsPbX_3 can be modified by the quantum-confined Stark effect.⁹⁷⁵ Nonetheless, the exact relationship between blinking and A-site cation in an MHP QD is yet to be verified.

Photoluminescence Blinking in MHP Single Crystals and Microcrystals.

As outlined in the previous section, photoluminescence blinking on time scales up to seconds or minutes is an established phenomenon for single quantum systems such as molecules and classical QDs. Hence, the observation of blinking in larger MHP nano- and microcrystals was surprising, necessitating physical explanations beyond the mechanistic picture of blinking in quantum systems. In recent years, unraveling the underlying processes of blinking has become a topic of intense research. Even though full understanding of the physical picture is still absent, several key experiments have been carried out and yielded important information for the research on the origin of blinking. Moreover, blinking in spatially extended objects offers the distinctive opportunity to spatially resolve the intensity fluctuations and correlate them with the material's morphology.

Pioneering Work and General Picture. The initial studies on blinking in MHPs emerged in 2015 and focused on larger sized MAPbI_3 NCs and microcrystals (μCs),^{700,976} whereas MHP QD blinking was reported only a few months later.²⁶ With their observation of blinking in 2–3 μm long MAPbI_3 microrods, Zhu *et al.*⁷⁰⁰ reported for the time PL intermittency of MHP crystals larger than the diffraction limit of light. Tian *et al.*⁹⁷⁶ carried out more extensive research on the blinking phenomenon itself using polycrystalline MHP NCs. They suggested that the intensity fluctuations in such polycrystalline NCs are controlled by chemical or structural defects that trap-free charges.⁹⁷⁶ Due to their ability to quench the PL across surprisingly large volumes of MHP NCs and even μCs , Merdasa *et al.*⁹⁶³ later termed these presumable defects “supertraps”. There is a clear analogy to large organic systems like conjugated polymers and aggregates, as in both cases the excited states are not delocalized over the whole volume ($100 \times 100 \times 100 \text{ nm}^3$ or larger); however, the excitations are very mobile and can travel over almost the entire system and potentially undergo nonradiative decay *via* an active quencher.

Conceptually, this idea is similar to the model of MRCs proposed by Frantsuzov and Marcus.^{968,969} Originally, this model was invoked to explain the power-law distribution of switching times in QDs, which were inconsistent with the commonly accepted model of trap-assisted Auger recombination. As illustrated in Figure 116, the main idea is that the nonradiative rate fluctuates due to the ON/OFF switching of one or several metastable defects, leading to a time-dependent luminescence yield

$$\Phi(t) = \frac{k_r}{k_r + \sum_i k_{nr,i}(t)} \quad (1)$$

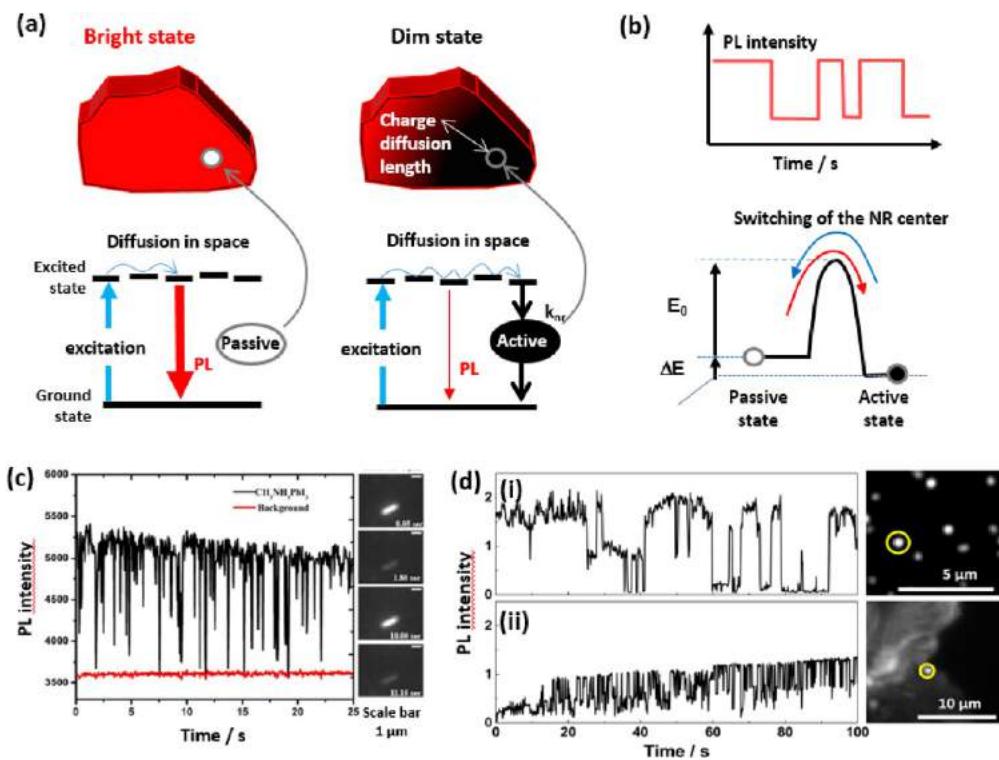


Figure 116. (a) Schematic illustration of the mechanism of a NR center in an MHP crystal and corresponding energy diagram schemes showing the sub-band-gap state formed by the defect. When passivated, the charge carriers freely diffuse until they recombine radiatively (bright state). When the NR center gets activated, a charge carrier can be “trapped” by the center due to the typical long charge carrier diffusion lengths in MHPs, experiencing a trap-assisted nonradiative recombination (dim state). (b) Typical recorded PL transient and corresponding energy diagram illustrating the energy barrier for “on/off” switching of the NR center. (c,d) Pioneering blinking experiments showing PL intensity time traces for (c) a single MAPbI₃ microrod ($\lambda_{exc} = 540$ nm, $\lambda_{PL} = 700$ nm). Reproduced from ref 700. Copyright 2015 American Chemical Society. (d) (i) MAPbI₃ nanocrystal and (ii) a bright dot located on the top of a polycrystalline MAPbI₃ crystal. Reproduced from ref 976. Copyright 2015 American Chemical Society.

where k_r denotes the radiative decay rate and $k_{nr,i}$ is the time-dependent nonradiative rate constant for an active defect. In larger crystals, it is important to consider that Φ may also have some spatial dependence due to the spatial distribution of nonradiative recombination centers and a limited diffusion of photoexcited carriers toward these centers.

Tian *et al.*⁹⁷⁶ estimated the “quenching volume” of their polycrystalline MAPbI₃ NCs to be $>10^{-16}$ cm³ and the concentration of quenchers to be $<10^{16}$ cm⁻³. From the saturation of blinking at high excitation power, the authors also estimated the capacity of the quenchers, *i.e.*, the maximum nonradiative recombination rate, to be 10^8 s⁻¹, corresponding to the quenching of one electron–hole pair per 10 ns. Later, similar estimates yielded quencher concentrations of 1.6×10^{16} cm⁻³ in the study of Gerhard *et al.*⁹⁷⁷ Hence, even for defect-rich polycrystalline MHPs of several hundred of nanometers in size, there is only a relatively small number of metastable quenchers per crystal.^{977,978} Note that the defect concentration is highly dependent on the synthesis procedure and the crystallinity of the formed MHP crystals, which is reflected in the variety of numbers reported here.

Similar to small NCs, Yuan *et al.*⁹⁷⁹ encountered power-law distributions of active and passive time periods exceeding 2 orders of magnitude upon blinking of large-sized MAPbI₃ NCs. Moreover, Yuan *et al.*²¹ as well as Merdasa *et al.*⁹⁶³ confirmed the time fluctuations of the nonradiative rate by correlating the appearance of intermediate PL intensity levels in the blinking transient to faster PL decay. Faster PL decay in connection

with a lower PL intensity is expected when the PL yield is modulated by a fluctuating nonradiative rate according to eq 1.

After introducing these NR centers, we would like to reiterate why the blinking in MHP nano- and microcrystals must have different underlying mechanisms to blinking in MHP NCs. As outlined before, PL blinking is commonly ascribed to the Auger process in colloidal QDs with sizes in the range of 2 to 7 nm. After the creation of a trion, subsequently excited electron–hole pairs will recombine nonradiatively by transferring their excitation energy to the extra charge *via* an Auger process, instead of emitting a photon. This “dark” state of the crystal lasts until the MHP QD turns back to the neutral state by recapturing the charge. Switching of the QD between the charged state and the neutral state can take several seconds and the process can therefore be easily framed.

For the Auger process to occur, the charges must be confined in a very small volume on the order of 100 nm³, which corresponds to a charge concentration of 10^{19} cm⁻³. This is exactly the regime of carrier concentrations when charge recombination in a bulk semiconductor is dominated by the Auger process. In MHP crystals with dimensions on the order of 100 nm length or larger, the carrier concentrations are orders of magnitude lower (10^{13} to 10^{16} cm⁻³). Even if the crystals become charged, the extra charges do not increase the carrier concentration close to the Auger regime. Reaching sufficiently high carrier densities is possible by choosing appropriate excitation conditions (> 100 W cm⁻²), however, this would not lead to “digital” switching of the nonradiative

rate, because the process is masked by the high number of other recombination events. Therefore, a much larger volume requires a different mechanism to explain PL blinking. Moreover, the absence of the photon antibunching effect in MHP sub-micrometer-sized crystals recently demonstrated by Eremchev *et al.*⁹⁸⁰ rejects the simple Auger-based blinking mechanism. An alternative mechanism is trapping by a strong NR center, which is metastable and works at any excitation condition as long as the trap is not saturated. The only requirement is that the charge carrier should be able to diffuse over the whole volume of the crystal to reach the center.

Origin of Metastable Defects. The idea of metastable NR centers has become the basis of the current understanding of PL fluctuations in MHP NCs. However, the chemical origin of the underlying defects has not yet been unraveled. It is important to note that the blinking phenomenon is not restricted to prototypical MAPbI_3 , but rather seems to occur in a wide variety of MHP compositions and morphologies.

Wen *et al.*⁹⁸¹ reported blinking in local regions of a polycrystalline film comprising MAPbBr_3 NCs, whereas intermittency in isolated NCs was suppressed. In that early work, the authors assigned the dim intervals to enhanced Auger recombination at interfaces between NCs in the film where charge carriers get accumulated in analogy to the blinking of aggregates of QDs.^{26,964,966,970} However, as we have discussed before, Auger recombination cannot be the primary origin of blinking in large crystals because of their size. Freppon *et al.*⁹⁸² studied the PL intermittency in pure MAPbI_3 and MAPbBr_3 NCs, as well as in NCs with mixed-halide composition. The PL in the pure components was stable, while the mixed compounds showed pronounced blinking behavior, most likely due to (light-induced) iodide-rich and bromide-rich phase segregation. Tachikawa *et al.*⁹⁸³ on the other hand reported blinking for individual MAPbBr_3 NCs, which was accompanied by light-induced PL enhancement. Halder *et al.*⁹⁸⁴ observed blinking in both pure and SCN^- -doped MAPbI_3 NCs, and Li *et al.*⁹⁸⁵ demonstrated PL intermittency behavior in individual grains of mixed-halide $\text{MAPbI}_{3-x}\text{Cl}_x$ films. The above-mentioned studies confirm that the blinking phenomenon occurs in a plethora of MHP systems, which indicates that it is a general feature of MHP semiconductors related to the presence of a small number of metastable NR centers per grain/crystal⁹⁷⁸ rather than an effect, which is limited to certain material compositions or morphologies.

A very informative approach to comprehend the origin of metastable defects is the study of blinking in different atmospheric conditions, as they provide different reactive environments for trap formation and annihilation, in particular at the crystal surface. Yuan *et al.*⁹⁷⁹ investigated the environmental dependence of blinking in single-crystalline MAPbI_3 nanorods and found pronounced differences in the blinking behavior under vacuum, nitrogen and ambient air (Figure 117). From this they concluded that most of the defects causing PL blinking must be located close to crystal surface. As potential candidates for the metastable defects they proposed under-coordinated Pb ions and MA vacancies. For the formation of the latter species, they argued that vacuum could promote detachment of MA due to its low boiling point, whereas the presence of oxygen, light and moderate humidity enable chemical reactions that promote passivation of surface defects. Passivation of defects under these atmospheric conditions has also been reported by Tian *et al.*,⁹⁸⁶ Tachikawa *et al.*,⁹⁸³ and Merdasa *et al.*⁹⁶³ who found an increase of the

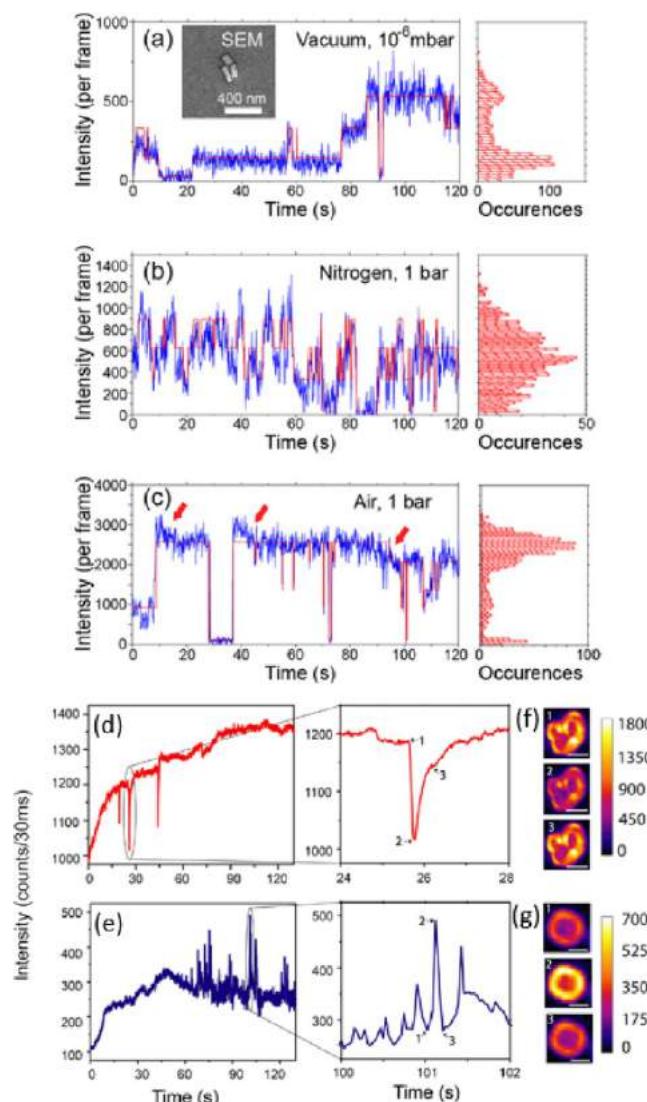


Figure 117. Effect of environmental conditions on PL blinking time traces of MAPbI_3 nanorods (a) under vacuum, (b) in nitrogen under ambient pressure, and (c) in air under ambient pressure. The inset shows the scanning electron micrograph of the cluster of three perovskite nanorods. The red lines are a guide for the eye. Reproduced from ref 979. Copyright 2016 American Chemical Society. (d–g) Slow, gradual PL flickering of MAPbBr_3 microcrystals under different humidity conditions. PL intensity time traces showing exceptional (d) sudden dim states under low humidity conditions (35–70% RH) and (e) sudden bright states under high humidity conditions (75–90% RH). (f,g) PL images of the particular microcrystals from (d,e) respectively, with timing of 1, 2, and 3. Scale bar = 1 μm . Reproduced from ref 989. Copyright 2016 American Chemical Society.

overall PL intensity and connected this to the emergence of blinking. Although, it is important to realize that fast diffusion of gases like oxygen through MHP crystals does not allow to assign the effect of atmosphere to surface modification only. The influence of surface defects on the PL are consistent with surface passivation studies leading to a significant improvement of the luminescence yield and optical stability.^{983,987,988} However, note that not all metastable defects were passivated, potentially because some of them are inherent structural defects, as pointed out by Yuan *et al.*⁹⁸⁷

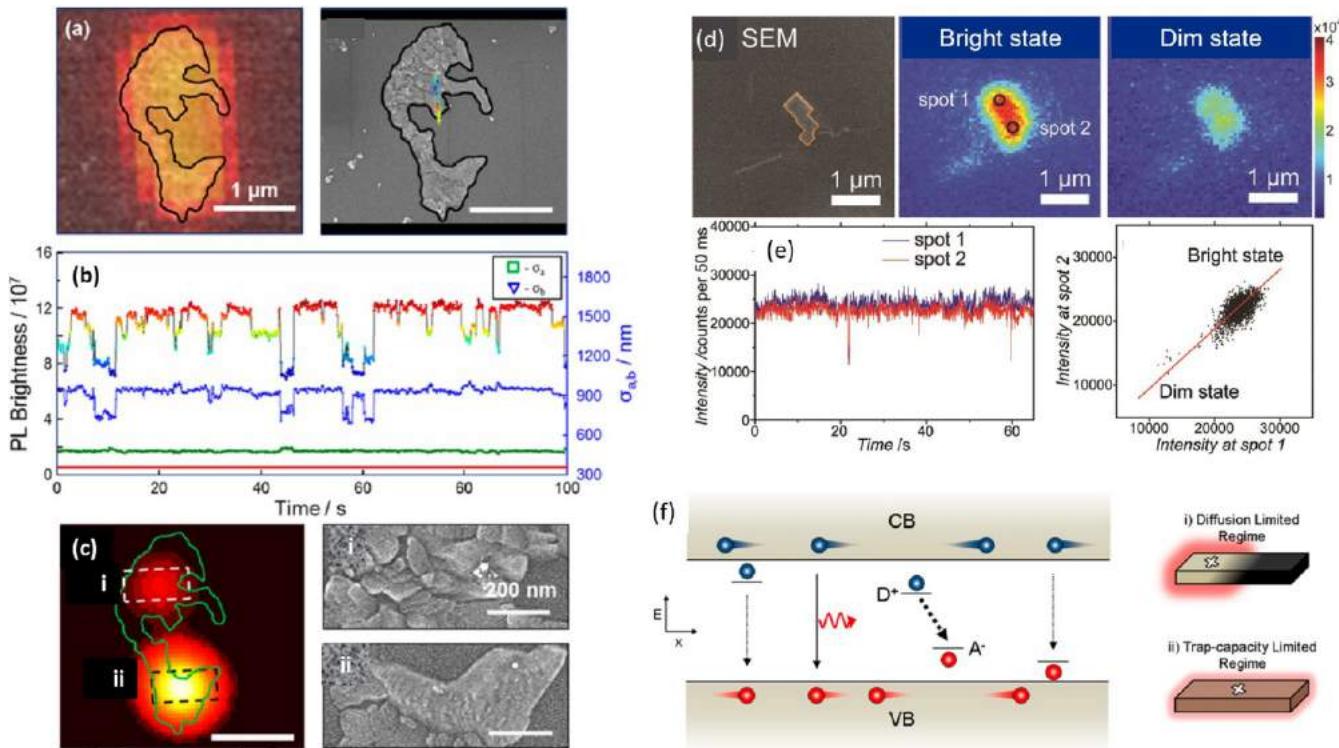


Figure 118. (a) PL emission profile of a large MAPbI₃ polycrystal with its contour shown by the black line (left) and the emission localizations indicated on the corresponding SEM image (right). (b) PL intensity transient and time dependence of the Gaussian widths ($\sigma_{a,b}$) indicating a fluctuating asymmetric emission profile. The red horizontal line at 360 nm is the σ_{PSF} of the microscope for $\lambda = 760$ nm. (c) SOFI image showing two well-separated spots (left) and their corresponding zoomed-in SEM images (right). Reproduced from ref 963. Copyright 2017 American Chemical Society. (d) SEM image of a polycrystalline MAPbI₃ NC with a volume of about 9×10^6 nm³ and the PL images in its bright state and dim state, respectively. (e) PL intensity time traces recorded at the two ends of the crystal (left) and scatter plot of the PL intensities at both ends showing a strong correlation (right).⁹⁸⁷ Reproduced with permission from ref 987. Copyright 2018 John Wiley & Sons, Inc. (f) Schematic illustration of a high-capacity NR center (supertrap) as a donor-acceptor pair. Left: Energy diagram schemes showing the sub-band-gap states formed by the defects. In the case of an ionized donor (D⁺) and acceptor (A⁻), the high-capacity NR center is created and efficient nonradiative recombination occurs (thick dashed line). If they are separated in space, nonradiative recombination is inefficient (thin dashed lines). Radiative recombination occurs across the band gap (solid line). Right: Different operational regimes of the high-capacity NR center as affected by its location (white crosses). Reproduced from ref 963. Copyright 2017 American Chemical Society.

Detailed studies on the influence of the ambient atmosphere on MAPbBr₃ microcrystals were also carried out by Halder *et al.*⁹⁸⁹ In particular, they investigated the effect of high humidity and observed a lower PLQY in a humid atmosphere and the appearance of strong variations in the PL intensity looking like PL flickering. This process was found to be accelerated in the presence of oxygen. Upon the removal of moisture, the flickering disappeared, accompanied by a considerable enhancement in the overall PL intensity. It is important to note that the change in PL was usually gradual rather than abrupt, thus it cannot be explained by activation/deactivation of just one quencher. In this work, the slow PL flickering was assigned to a concerted phenomenon caused by several defects. Such defects may be induced *via* interaction with the environment, for example, transient chemical changes to the surface layer due to local fluctuations of humidity. So far, all these are pure speculations and further studies are needed to understand the nature of such large-scale gradual fluctuations. It is interesting to note that the emergence of PL flickering observed by Halder *et al.* was connected to an overall reduction of the PL intensity due to the humidity effect, whereas in the other reports mentioned above,^{963,983,986} PL blinking appeared after light-induced PL enhancement. This is a strong indication that the flickering phenomenon observed by Halder *et al.*

under high humidity has a different origin from “real” blinking related to individual luminescence quenchers, which becomes more pronounced after PL enhancement potentially due to light-induced defect curing, which increases the diffusion length and with this the quenching volume of individual metastable quenchers.

Variations of the experimental conditions can also be employed to study whether blinking is a photo- or thermally activated process. Tian *et al.*⁹⁷⁶ and Yuan *et al.*⁹⁷⁹ studied the influence of optical power on the blinking characteristics. Both found a strong reduction of the relative blinking amplitudes, which was interpreted as a saturation of the metastable nonradiative center (trap filling) and an overall reduction of blinking events with increasing excitation power. Photoactivation, however, would become apparent as an increase of the switching dynamics. Hence, in recent studies there is no evidence for photoactivation of the switching process. However, trap filling effects could mask the photoactivation phenomenon and more suitable model systems, *e.g.*, smaller crystals, are needed to clarify this point.

By investigating the influence of temperature on luminescence blinking, Gerhard *et al.*⁹⁷⁷ provided a detailed view on the underlying mechanism of blinking in MAPbI₃ NCs. After decreasing the temperature from 295 to 77 K, an increased

time-averaged PL intensity by 1–2 orders of magnitude was observed as well as a substantial reduction in the relative magnitude of blinking below 200 K. Both the observed temperature-dependent PL intensity and the blinking dynamics were very specific from crystal to crystal and often fully repeatable in consecutive cooling–heating cycles. It was proposed that this peculiar behavior comes from the presence of several quenchers per crystal having potential barriers between active and passive states. Using a simple model, the activation energies of the switching of individual quenchers were found to be broadly distributed from 0.2 to 0.8 eV. This range matches the range of reported energy barriers for ion migration in perovskites. Therefore, it is likely that the random switching is caused by diffusing ions that can passivate or activate an NR center, whose energetic position is determined by the local environment.

Even though the above-mentioned studies revealed important insights into the processes that drive luminescence blinking, the nature of the underlying defects has not yet been defined. It is important to note that most MHPs possess defect levels close to the band-edges. Therefore, it is unlikely that they act as potent luminescence quenchers. However, as pointed out by Merdasa *et al.*,⁹⁶³ one should consider that the defects could also be complexes comprising an electron donor and an electron accepting species. This way, electrons and holes are efficiently trapped in close proximity, and their spatial overlap leads to fast nonradiative recombination. Additionally, this hypothesis seems to explain the relatively low estimated concentration of metastable NR centers.

Super-resolution Methods to Unravel the Spatial Distribution of NR Centers. The fact that blinking in MHPs occurs in spatially extended objects offers the opportunity to obtain information about the location of quenchers and emissive sites. In this context, a particularly powerful approach is the combination of electron microscopy with super-resolution fluorescence microscopy,^{963,979,987} which allows for the direct correlation between the morphology of the material and the local emissive properties.

In their study on monocrystalline MAPbI₃ NCs, Yuan *et al.*⁹⁷⁹ recorded SEM images and employed a localization algorithm to track the center of the profile emission in the course of blinking. Interestingly, they found no change in the emission localization position upon blinking of single crystals. In contrast, for polycrystalline MHP NCs, Tian *et al.*⁹⁷⁶ observed a clear correlation between the PL intensity fluctuations and shifts in the emission location. In the first case carrier diffusion through the whole crystal is very efficient and the extent of luminescence quenching is only limited by the capacity of the metastable defect. As a consequence, the PL of the crystal is spatially homogeneously quenched. In the second case charge carrier diffusion plays a crucial role such that quenching in some regions of the objects is more efficient than in other regions, leading to shifts of the emission location in the course of blinking. The existence of both quenching regimes was initially pointed out by Merdasa *et al.*,⁹⁶³ who presented an extensive study on PL blinking in polycrystalline MAPbI₃ microcrystals (Figure 118a–c), as well as monocrystalline microrods up to 10 μm in length. The authors demonstrated experimentally clear examples of the diffusion-limited and the NR center capacity-limited blinking regimes, as illustrated schematically in Figure 118f. It was found that high-capacity NR centers, also termed “supertraps”, are most efficient in structurally homogeneous and large MAPbI₃

crystals where carrier diffusion is efficient, which may pose limitations on the efficiency of perovskite-based devices. Furthermore, as can be found in Figure 118f, they have elaborated a scheme considering the high-capacity NR center or supertrap as a donor–acceptor pair.

Sharma *et al.*⁹⁹⁰ demonstrated electroluminescence blinking in aggregated CsPbBr₃ NCs but noted the absence of blinking when the material was photoexcited. By employing a super-resolution technique, they found that the electroluminescence was emitted from only a few distinct spots in each aggregate. They attributed this to the fact that, in the case of electroluminescence, only a few of the agglomerated NCs are emissive due to funneling of the injected charges to the lowest energy levels. PL on the other hand resulted from collective excitation of the overall aggregates, hence, no fluctuations of individual NCs became apparent. Their work further exemplifies that a key requirement to observe blinking is a high interconnectivity between the emissive entities, or, in other words, efficient diffusion of a major fraction of the emissive population toward the quenching defect.

In addition to localization of the emission position, other techniques borrowed from the toolkit of super-resolution methods have been employed to study the blinking dynamics. Tian *et al.*⁹⁸⁶ utilized a differential super-resolution technique to spatially map the regions characterized by intense PL blinking in a polycrystalline MAPbI₃ film and found that the emission predominantly stems from very localized sites of less than 100 nm in size. It was hypothesized that an emitting site can be either a small crystallite free from quenchers or a spatially localized state in a large crystal with increased radiative recombination probability. Merdasa *et al.*⁹⁶³ employed super-resolution optical fluctuation imaging (SOFI) to detect local regions with strong and frequent blinking in polycrystalline MAPbI₃ NCs. As depicted in Figure 118d,e, Yuan *et al.*⁹⁸⁷ used a differential imaging approach similar to that of Tian *et al.*, from which they determined a heterogeneous distribution of fluctuating quenchers in mono- and polycrystalline objects comprising MAPbI₃. Interestingly, the authors demonstrated that even a micrometer-sized polycrystal comprising several well-defined cubic sub-micrometer crystals can generate one common PL blinking time trace which is not limited by diffusion.

The combination of SEM with super-resolution fluorescence allowed furthermore to directly correlate the location of the NR center to a specific blinking volume, allowing to precisely define the density of NR center. As such, Merdasa *et al.*⁹⁶³ estimated a 10^9 s^{-1} recombination rate introduced by a single quencher (supertrap) and Yuan *et al.*⁹⁸⁷ obtained quencher densities of 8.5×10^{13} and $1.3 \times 10^{14} \text{ cm}^{-3}$ for monocrystalline and polycrystalline NCs, respectively. The discrepancies in the reported defect concentrations highlight once more the importance of the material quality. Additionally, the crystal morphology and size may play a role. For smaller crystals, defects with a smaller capacity cause detectable PL blinking, while in larger crystals their influence can be suppressed because they get saturated at the same excitation power due to larger number of electron–hole pair generated in the crystal.

Electron–Phonon Coupling in Single Perovskite NCs. The intrinsic (photo)physical properties of MHP semiconductors are strongly related to the coupling of excited electronic and vibrational states.⁹⁹¹ The vibrational modes in MHPs can be generally split into two branches:^{992,993} a low-energy band (20–200 cm^{-1}) dominated by the inorganic

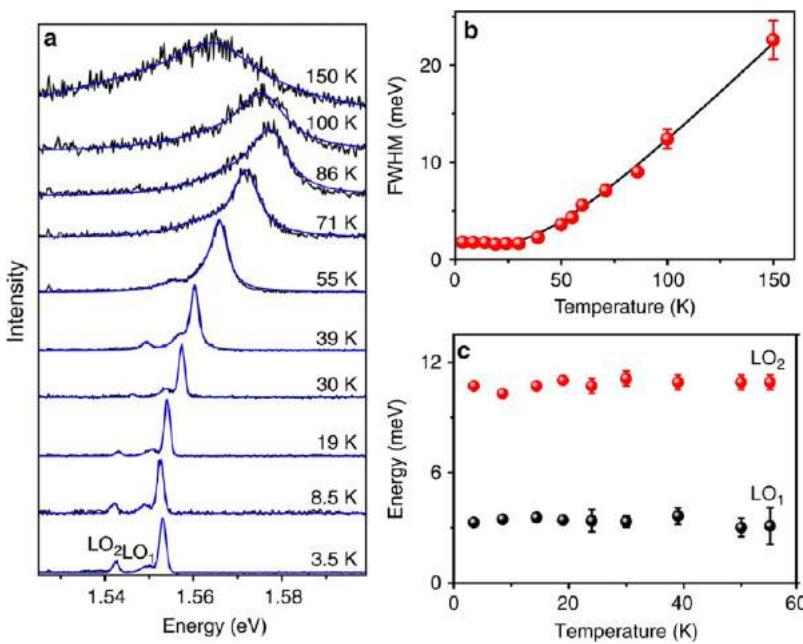


Figure 119. Temperature-dependent PL (a) spectral evolution and (b) zero-phonon PL (ZPL) line width (fwhm) of a single FAPbI₃ NC. The black line is a fitting curve made using eq 2, taking into account only the low temperature line width ($\Gamma_0 = 1.5$ meV) and Fröhlich coupling contributions ($E_{LO} = 10.7$ meV). Broadening due to acoustic phonon scattering is found to be negligible. (c) LO₁ and LO₂ phonon energies as a function of temperature from 3.5 to 55 K, recovered from (a). Reprinted with permission under a Creative Commons CC BY 4.0 license from ref 997. Copyright 2018 The Authors.

[PbX₆]⁴⁻ sublattice, along with the high-energy vibrations of the organic components (200–3300 cm⁻¹). In all-inorganic systems, like the CsPbX₃ perovskites, the high-energy branch is missing. Following the absorption of above band gap light,⁹⁹⁴ the thermalization, transport, and recombination of photo-generated carriers will depend on the underlying electron–phonon interactions. For instance, stronger electron–phonon scattering in lead-based [PbX₆]⁴⁻ octahedra directly reduces carrier mobility and increases the PL emission Stokes shift and line width (*i.e.*, color purity). At relatively low temperatures (below ~50 K), scattering from low-energy acoustic phonons is dominant, while closer to RT Fröhlich coupling with high-energy longitudinal optical phonons ($E_{LO} = \hbar\omega_{LO}$) is the principal scattering mechanism in polar MHPs.

Analysis of the PL fwhm between 0 K and RT has become routine for gauging the strength of electron–phonon coupling within MHPs and comparing its magnitude across different compositions.^{795,995} The temperature-dependent excitonic line width of band to band recombination within semiconductors^{795,798,996} is related to the carrier–phonon coupling by

$$\Gamma(T) = \Gamma_0 + \gamma_{ac}T + \gamma_{LO} \frac{1}{e^{E_{LO}/k_B T} - 1} \quad (2)$$

The first term (Γ_0) represents the intrinsic low-temperature fwhm, while the second and the third terms (Γ_{ac} and Γ_{LO}) describe acoustic and LO–phonon (Fröhlich) scattering contributions, respectively, with coupling strengths γ_{ac} and γ_{LO} . Below 75 K, the linear Γ_{ac} component dominates due to low-energy acoustic phonons. The LO–phonon population requires more thermal energy to become impactful, being governed by Bose–Einstein statistics, with k_B being the Boltzmann constant.

Studying single MHP NCs also allows one to investigate electron–phonon interactions beyond the bulk approximation. In the absence of strong thermal broadening close to 0 K,

electron–phonon coupling in MHP NCs can manifest additional satellite peaks in the high-resolution PL spectrum, appearing as low-energy phonon replicas.^{997,998} These additional peaks correspond to weak phonon-assisted transitions and are red-shifted relative to the central zero-phonon PL (ZPL) emission. The relative intensity of phonon replicas between different NCs of different sizes will vary.⁹⁹⁹ Whereas low-temperature PL spectroscopic studies are widely adopted to probe electron–phonon interactions in MHPs, relatively few studies have focused on single MHP NCs. At the nanoscale, perovskite crystals tend to exhibit higher phase stability, preferring to occupy the desired perovskite structure,³ allowing more complete low-temperature optical studies. Furthermore, for micro-PL studies on single MHP NCs, the emission fwhm is substantially reduced^{997,1000–1003} (≤ 1 meV) compared to ensemble NC studies, better revealing fine energetic structure.

Temperature-Dependent PL. In Figure 119a Lounis *et al.*⁹⁹⁷ examine the thermal evolution of the exciton-phonon coupling phenomena in individual FAPbI₃ NCs. Interestingly, below 30 K, they found negligible thermal broadening in the ZPL emission from a single FAPbI₃ NC (Figure 119b), which suggests a weak electron–acoustic phonon interaction. An upper limit of $\gamma_{ac} \sim 5 \mu\text{eV K}^{-1}$ is extracted from eq 2 from their temperature-dependent broadening, which is found to be over 1 order of magnitude smaller than that previously reported for bulk FAPbI₃.⁷⁹⁵ Thus, using a single optical phonon mode is enough to reproduce the thermal-induced broadening evolution in Figure 119b (parameters: $\Gamma_0 = 1.5$ meV, $\gamma_{ac} = 0$ meV, $\gamma_{LO} = 27$ meV, and $E_{LO} = 10.7$ meV). While the optical phonon energy appears to be softened in the NC, the γ_{LO} broadening coefficient derived is in agreement with measurements on bulk FAPbI₃.⁷⁹⁵ Due to the location of the A-site cation within the charged octahedral cavity formed by the BX₃ sublattice, MHP NCs exhibit a soft ionic structure which

endow them with so-called “crystal–liquid duality”.¹⁰⁰⁴ More specifically, this glass character arises from the crystalline-like response of coherent band transport and a liquid-like response in the dielectric function. Hence, Fu *et al.*^{997,1005} assigned the derived smaller γ_{ac} value to the phonon glass character of the soft perovskite lattice and the larger bulk values to extrinsic influences (counterintuitive to expected confinement effects¹⁰⁰⁵), rather than intrinsic electron–phonon interactions.

Below roughly 60 K, the appearance of additional phonon replicas are also resolved in the single FAPbI₃ NC⁹⁹⁷ PL spectrum, assigned to different bundles of separated low-energy lattice modes (Figure 119c). On the basis of theoretical predictions and low-temperature vibrational studies of APbI₃-based systems, they assign these phonon replicas to different bundles modes which are seen to be thermally stable in Figure 118c. Up to three additional satellites were resolved during their survey,⁹⁹⁷ being governed by different bending and stretching modes of the PbI₆ network and motion of the organic FA cation, and by their mutual couplings.

Through PL studies of individual all-inorganic CsPbBr₃ microwires at cryogenic temperatures (77 to 300 K), Zhao *et al.*¹⁰⁰⁶ revealed the electron–phonon interactions arising in wires ranging from 0.5 to 5 μm thick and up to hundreds of microns long. They found that the PL spectrum exhibited a dominant green (527 nm) triplet exciton emission with an additional low-energy shoulder (\sim 540 nm) which became better resolved at lower temperatures, due to a replica emission. Fitting the thermal-induced broadening of the ZPL emission down to 77 K in the single CsPbBr₃ microwires, they extracted an LO–phonon coupling constant of $\gamma_{LO} = 66$ meV¹⁰⁰⁶ using a thermally stable phonon energy⁹⁹⁶ of $E_{LO} = 19$ meV, as derived from the single-crystal Raman scattering spectrum. This value is comparable to other bulk lead-bromine-based perovskites⁷⁹⁵ and confirms the preservation of strong Fröhlich interactions in their single CsPbBr₃ microwires, arising from relatively weak confinement effects, *i.e.*, due to the relatively large NC dimensions.

Rainò *et al.*¹⁰⁰⁰ reported one of the low-temperature PL studies of single MHP NCs, examining individual all-inorganic CsPbX₃ (X = Cl/Br) NCs. Beyond the interesting blinking phenomena exhibited by the NCs, spectra measured from a single particle using sufficiently high optical excitations contained an additional low-energy peak, arising from a charged excitonic emission. Measured at what they define as intermediate excitation power,¹⁰⁰⁰ the charged exciton line of some NCs became 2–3 times narrower than the principal exciton line, suggesting that the excitonic transition might have reduced electron–phonon coupling. At the single FAPbBr₃ NC level, Pfingsten *et al.*¹⁰⁰¹ examined exciton–phonon interactions *via* temperature- and polarization-dependent PL measurements. Near 0 K, pronounced satellite PL peaks appear shifted relative to the ZPL band due to the TO₁, TO₂, and TO₃/LO₁ phonon bands, by energies of 4.3, 8.6, and 13.2 meV, respectively. Through their survey of multiple individual NCs, some extra replica peaks sometimes appeared, red-shifted by higher energies (18.3 and 37.2 meV) relative to the ZPL.¹⁰⁰¹ Based on the expected low-energy vibrational modes of the PbBr₆ octahedra, they attribute these additional emission peaks to coupling of charge carriers to libration modes of the FA⁺ cations. Fitting the temperature-dependent fwhm of the ZPL with eq 2, Pfingsten *et al.*¹⁰⁰¹ also inferred a negligible contribution from acoustic phonon coupling ($\gamma_{ac} < 0.1$ meV) and identified thermal-induced broadening to

principally arise *via* an optical phonon coupling constant (γ_{LO}) of roughly 32 meV. Notably again, the optical phonon contribution is recorded here to be relatively low compared to other bulk Br-based MHP counterparts.⁷⁹⁵

Employing low-temperature (down to 5 K) polarized PL studies of CsPbBr₃ single NCs (\sim 7 nm), Ramade *et al.*¹⁰⁰² also found that the temperature-dependent PL line width is mainly governed by the Fröhlich term ($\gamma_{LO} = 42 \pm 15$ meV), being consistent with the polar nature of the bulk lead-halide perovskite.⁷⁹⁵ Within this regime (*i.e.*, NCs exhibiting band gaps of 2.46–2.62 eV), they found no correlation of the crystal size, for NCs in the order of the Bohr diameter, with the PL broadening due to acoustic phonon coupling. Liu *et al.*¹⁰⁰³ reported single-dot PL measurements of MAPbI₃ NCs (\sim 7 nm) down to 5 K, realizing the narrowest ZPL line width of \sim 0.6 meV ever managed in the archetypal perovskite system. They also noted a sharp satellite peak that was red-shifted by \sim 4 meV in low-temperature spectra, which varied in relative amplitude between dot to dot, pointing to variation in their exciton–phonon coupling strengths.

Summary and Outlook for Single-Particle Studies of MHP NCs. Photoluminescence blinking of MHP NCs hampers the application of these bright luminescent crystals in quantum optical devices. Spectrally and temporally correlated single-photon counting through single-molecule microscopy and spectroscopy have been helpful for the classification of the emitting states and the blinking mechanisms. Although single NCs emit entangled photons with slightly different energies from the band-edge triplet states which become nondegenerate when cooled significantly, the degree of degeneracy increases with temperature and the second-order single-photon correlation function minimizes at room temperature. Thus, the blinking mechanism of MHP NCs is dissected at room temperature. Photo-charging followed by nonradiative Auger recombination is the primary mechanism of blinking in metal-halide perovskite NCs and metal chalcogenides. Here, blinking is due to the random switching of a NC between nonradiative and radiative cycles by charging and discharging. Also, MHP NCs show blinking due to trap-assisted nonradiative carrier recombination involving surface traps, deep traps and shallow traps, governed by ion vacancies, interstitial sites and antisites. Hence, post-synthetic chemical modification of MHP NCs allows for blinking suppression. Nonblinking MHP NCs for applications in nanophotonic quantum devices can be developed by optimizing the energy and intensity of excitation light, the nature and density of trap states, the size of quantum dots and the chemical composition of cations, halide ions, ligands, and shells.

The growing number of studies related to PL intermittency in MHPs indicates that the phenomenon is an intrinsic feature of this material class rather than an effect related to specific processing conditions or a specific environment. Furthermore, it is important to note that blinking in crystals with sizes beyond quantum confinement (up to several micrometers) goes mechanistically beyond the physics and chemistry of single quantum systems. A consistent explanation for blinking in MHP nano- and microcrystals can be given by the presence of metastable nonradiative centers. Metastability of defect states is in fact reflected in many phenomena observed in MHPs and related devices, for example PL enhancement and suppression, ion migration, self-healing after photodegradation, dropping and recovery of solar cell efficiencies¹⁰⁰⁷ and the

sensitivity of these processes to light illumination, atmospheric constituents and temperature. Thus, it is plausible that PL blinking is another manifestation of the metastable character of incorporated defect states. Except for PL blinking, however, all defect-related phenomena are ensemble observations, where contributions of individual defects are averaged out. This averaging is unavoidable because of the very large number of individual species in the volume, which can be described by the concentration n . Now, let us hypothetically decrease the volume of the sample to $1/n$. Following Poissonian statistics, a crystal of this volume should contain on average 1 NR center, and its metastability becomes apparent as discrete blinking. To investigate this individual defect, methods of luminescence microscopy and in particular techniques inspired by super-resolution methods and single molecule spectroscopy are ideal tools. The resolution of optical microscopy is about 500 nm, which is equal to the typical grain size in polycrystalline films. Moreover, isolated crystals of sizes from 10 to 1000 nm can be readily investigated as model systems representing individual constituents of a perovskite film. Studying individual defects incorporated in these objects allows us to rationalize fundamental properties behind solar cells and other devices.

Furthermore, correlating PL and electron microscopy allows estimating the quenching volume and defect concentration. Taking the inverse of the concentration, we obtain the cube-shaped volume containing only one defect to range from 10^{-10} to 10^{-17} cm³, giving cube side lengths from 4.6 μ m to 21 nm. Grain sizes in MHP films vary over the same range, hence, a number on the order of one defect per grain appears reasonable. This estimation is nicely supported by the long list of experiments discussed above where strong PL fluctuations have been reported for MHP crystals of very different sizes up to micrometers. Note that in order to observe blinking, it is not necessary to have exactly one defect per crystal. Additionally, defects with the strongest quenching capacity will be more visible in the case of many defects contributing. Increasing the number of defects, however, will make the blinking transients more complex and eventually reduce the overall modulation of the luminescence yield, such that a number much higher than one appears unfeasible. Despite the uncertainty in determining the actual concentration of metastable quenchers, the current stage of experimental work indicates that there is a high variety in densities. Likewise, literature is filled with very divergent estimations of the defect state concentrations in MHPs based on distinct techniques, ranging from 10^{10} to 10^{17} cm⁻³, which may be related to diversity from poly- to monocrystalline crystals, different detection techniques, and different methods of data analysis. However, we note that it is a remaining open question whether blinking studies and other methods are actually sensitive to the same type of defects, whether or whether not being (high-capacity) NR centers.

Despite a growing number of studies related to blinking in MHPs, several questions regarding the phenomenon of blinking in MHP NCs and μ Cs remain open. These include in particular the nature of the metastable quenchers and the mechanism of their activation and deactivation. It has also not yet been studied whether the switching process can be activated by light. Better understanding of the origin of blinking can open channels to passivate the quenchers permanently, which will be beneficial for the performance of MHP devices. Another interesting question is which fraction of the defect states in MHPs is metastable. The defect

concentrations estimated from blinking experiments yield defect concentrations similar to the range reported from other methods, suggesting that the defects probed in blinking experiments are actually representative for a high fraction and maybe even all of the defects in the material. Furthermore, micro-photoluminescence studies on individual MHP NCs reveal high-resolution information on the nature and extent of charge carrier–phonon coupling in these systems, which are not averaged out by bulk measurements. Much deeper understanding of these photophysical processes can direct material development ensuring optimized charge dynamics with the aim to further design high-performance MHP NC-based optoelectronic devices.

APPLICATIONS

Lasers. Since the initial observation of stimulated emission (SE) and lasing from colloidal perovskite quantum dots (perovskite NCs), there has been a surge in research activities in developing high-performance perovskite NC-based lasers because perovskite NCs combine the advantages that can be derived from both colloidal NCs and halide perovskite materials, namely facile processability from solution, band gap tunability, large absorption cross-sections and low non-radiative recombination rates.^{28,1008–1018} In general, there are two kinds of halide perovskite NCs, that is, the organic–inorganic hybrid halide perovskites (OIHP) NCs and the all-inorganic halide perovskites NCs (IHPNs). The IHPNs manifest better stability against moisture and oxygen than OIHP NCs since the organic compounds tend to dissociate when exposed to ambient conditions. Until now, both the IHPNs and OIHP NCs have shown excellent optical gain performance and were used in a variety of laser devices, including random lasers,^{464,1019} whispering-gallery-mode (WGM) lasers,¹⁰²⁰ distributed feedback (DFB) lasers,^{1021–1023} vertical cavity surface emitting lasers (VCSELs),^{819,1014,1024,1025} and even high-resolution large-area laser arrays with multicolor outputs.^{696,1026}

In this section, we will discuss the optical gain in perovskite NCs including the SE under one- and multi-photon pumping as well as the optical gain mechanism. After that, the recent progress in laser devices developed from perovskite NCs will be presented. Finally, we will discuss the current challenges and perspectives of developing lasers based on perovskite NCs. We believe that perovskite NC-based lasers will become an important complement to epitaxial semiconductor lasers in the near future.

Optical Gain in MHP NCs. In 2014, SE was initially demonstrated in solution-processed $\text{CH}_3\text{NH}_3\text{PbX}_3$ (X = Cl, Br, and I) perovskite thin films, indicating that the halide perovskites are not only excellent photovoltaic materials but also promising gain media for lasing.^{53,176,1030,1031} Soon after, the notable optical gain properties of IHPNs were reported by Wang *et al.* and Yakunin *et al.* nearly simultaneously in 2015.^{28,1010} Both groups demonstrated robust SE under either femtosecond or nanosecond pulsed excitation from the close-packed thin films of CsPbX_3 IHPNs, where the thresholds were found to be much lower than those of the traditional CdSe-based NCs. The low SE threshold can be attributed to the large absorption cross section and the moderate nonradiative recombination loss (e.g., low rate of carrier trapping and relatively slow Auger recombination rate).^{28,1014} Leveraging on the variable stripe length technique, the modal gain in CsPbBr_3 NCs was determined to be as high as ~ 450 cm⁻¹. Moreover,

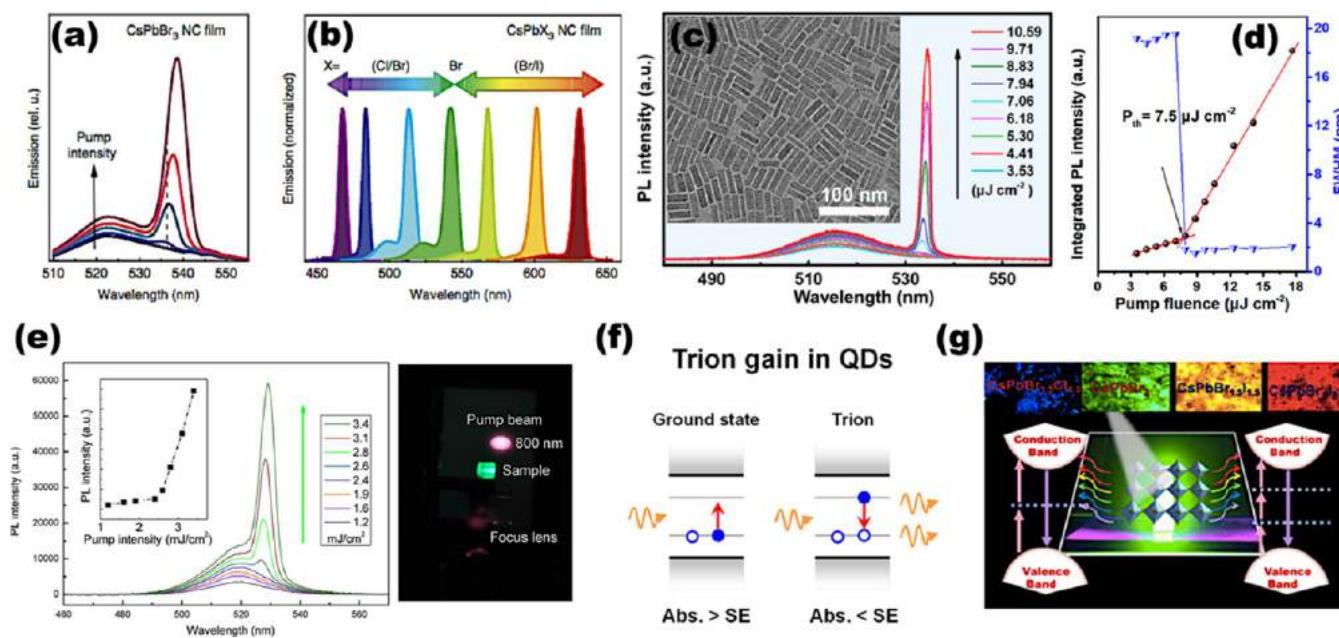


Figure 120. (a) Pump intensity dependence of the emission in a CsPbBr_3 NC film (pumping intensity range was 3–25 $\mu\text{J cm}^{-2}$). (b) Spectral emission tunability of ASE *via* modulating constituents in a CsPbBr_3 NC film. Reprinted with permission under a Creative Commons CC BY license from ref 1010. Copyright 2015 The Authors. (c) Pump-fluence-dependent emission of CsPbBr_3 perovskite nanorods with uniform surface. Inset: Typical TEM images of low-defect CsPbBr_3 nanorods. (d) Integrated PL intensity and line widths of CsPbBr_3 nanorods as a function of pump fluences. Panels c and d are reprinted from ref 1027. Copyright 2019 American Chemical Society. (e) Two-photon-pumped PL spectra from CsPbBr_3 nanocrystals at varied pump intensities. Right inset: Photograph of the stripe pumping configuration adopted to pump the CsPbBr_3 NCs with an 800 nm laser beam with the pulse width of 100 fs and repetition rate of 1000 Hz. Reproduced from ref 1011. Copyright 2015 American Chemical Society. (f) Mechanism for trion gain in singly charged NCs with doubly degenerate band-edge states. Reproduced from ref 1028. Copyright 2018 American Chemical Society. (g) Two-photon fluorescent microscope images of different CsPbX_3 Pe-NCs as well as the simple illustration of two- and three-photon-excited PL. Reproduced from ref 1029. Copyright 2019 American Chemical Society.

the SE spectrum can be easily tuned from blue, green to red region by adjusting the composition and size of IHPNs. (Figure 120a,b).^{28,1010} Later, using the intermediate monomer reservoir synthetic strategy, Wang *et al.*¹⁰²⁷ fabricated rod-shaped IHPNs. Thanks to surface ligand passivation, the perovskite nanorods showed a high PLQY of up to 90% and enhanced stability in aqueous environments and at high temperature, exhibiting an extremely high gain of 980 cm^{-1} and a low SE threshold of $7.5 \mu\text{J cm}^{-2}$ under nanosecond laser pumping, as shown in Figure 120c.^{1027,1032} In addition to the close-packed films of IHPNs, SE from the liquid solution of CsPbBr_3 NCs has also been reported recently. The SE threshold was estimated to be $105 \mu\text{J cm}^{-2}$, and photostability tests exhibited steady SE intensities for more than 3 h under the pump of a constant femtosecond pulsed laser beam ($>10^7$ shots).¹⁰³³ The superior gain properties of these IHPNs hold great potential for developing different classes of miniaturized laser devices.

Regarding the gain mechanism in IHPNs, Wang *et al.* performed comprehensive steady-state and time-resolved PL measurements and revealed that the optical gain might arise from the radiative recombination of biexcitons.²⁸ Lately, through two-dimensional electronic spectroscopy, Zhao *et al.*¹⁰³⁴ reported that the SE threshold in CsPbBr_3 NCs is largely determined by the competition between SE from biexcitons and excited-state absorption from single exciton to biexciton states. In other words, the optical gain in CsPbBr_3 NCs was confirmed to originate from biexcitons. The lower photon energy from biexciton recombination than single exciton transition as well as the relatively larger biexciton

binding energy from NCs makes IHPNs attractive candidates as optical gain media because the red-shifted SE peak could effectively reduce the reabsorption loss in an inhomogeneous NC ensemble. In addition, trion-based optical gain in colloidal CsPbBr_3 NCs was proposed by Wang *et al.* in 2018.¹⁰²⁸ Through surface treatment with excess PbBr_2 , the trion lifetime of the CsPbBr_3 NCs film was prolonged. At the same time, an ultralow SE threshold of $1.2 \mu\text{J cm}^{-2}$ (the average number of excitons per nanocrystal $\langle N \rangle = 0.62$, which is close to the theoretical threshold value of $\langle N \rangle_{\text{th}} = 0.58$ for trion-based gain) was observed, indicating the participation of trions in the optical gain. The schematic illustration of trion gain in NCs is shown in Figure 120f. Furthermore, single exciton recombination induced SE with threshold of $8\text{--}12 \mu\text{J cm}^{-2}$ in CsPbX_3 ($X = \text{Br}, \text{I}$) NCs has also been reported.¹⁰³⁵ The single-exciton gain mechanism leads to low optical losses, since the nonradiative exciton–exciton annihilation (Auger recombination) can be efficiently prevented, but the reabsorption loss may be an issue. Until now, the gain mechanism in Pe-NCs remains an open question, and more comprehensive spectroscopic studies correlated with theoretical calculations are required to reach a consensus. Nevertheless, the mechanisms of stimulated emission and lasing depend on the electronic structure of the particular material because different optical processes may compete with each other. There is no universal description of the mechanism for an inhomogeneous NC ensemble.

SE induced by two-photon and even high-order multiphoton absorption in perovskite NCs has also been extensively demonstrated in recent years, which highlights the potential

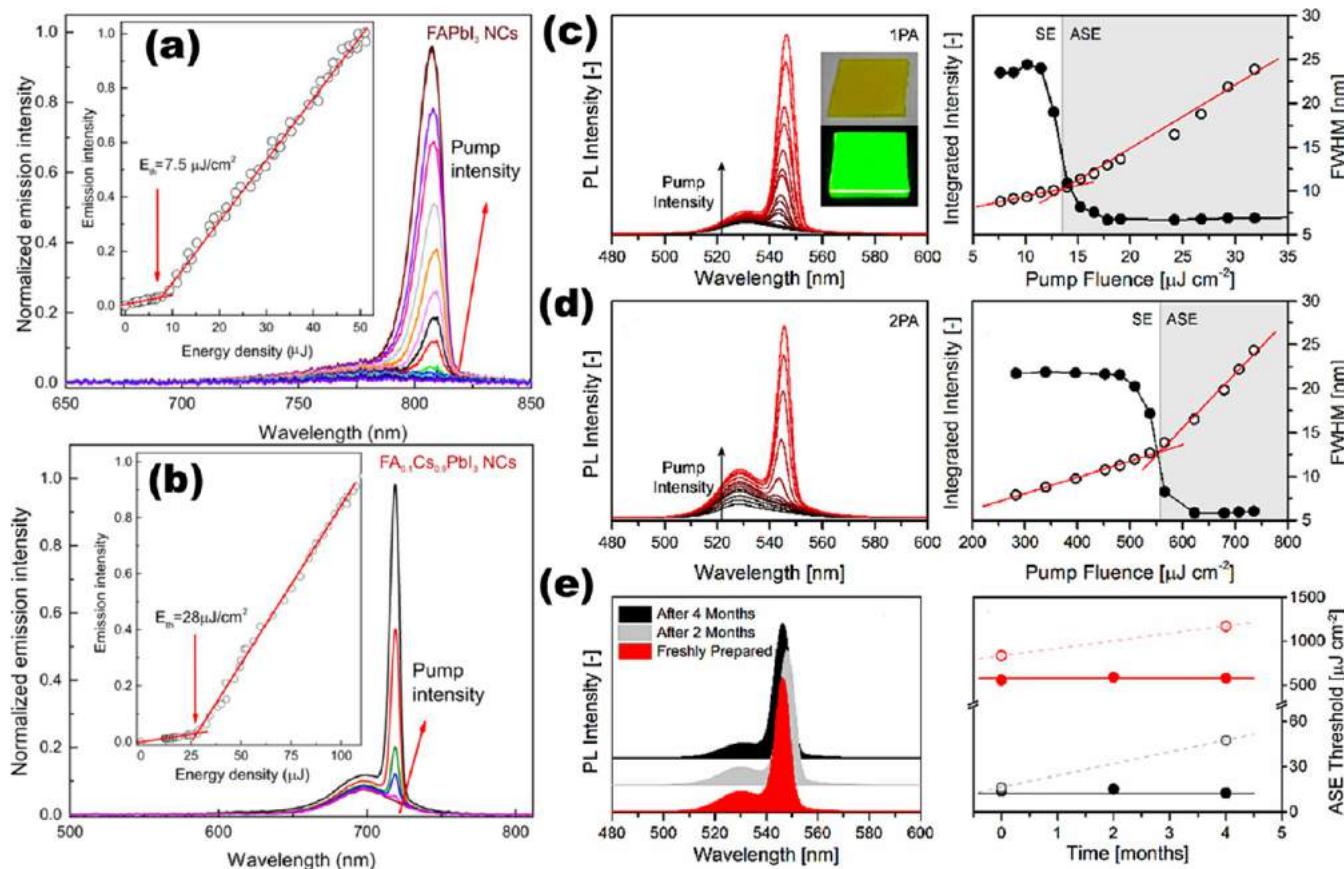


Figure 121. Emission spectra of (a) FAPbI₃ and (b) FA_{0.1}Cs_{0.9}PbI₃ NCs films pumped by a pulsed laser with duration of 100 fs, indicating the SE behavior with ultralow thresholds. The insets show the integrated PL intensity as a function of energy density. Reproduced from ref 69. Copyright 2017 American Chemical Society. Excited steady-state PL emission spectra of BnOH-modified MAPbBr₃ NCs under (c) one- and (d) two-photon absorption. (e) Consistency of steady-state PL and stimulated emission peak position and the corresponding ASE threshold of different month(s) old BnOH-modified MAPbBr₃ NC samples stored under ambient conditions. Reproduced from ref 1042. Copyright 2017 American Chemical Society.

of these materials for nonlinear photonics and devices.^{826,1011,1029,1036–1039} Multiphoton absorption is an important branch of nonlinear optics, which features long excitation wavelengths and nonlinear excitation intensity dependent fluorescence. Hence, it brings about the advantages of deeper penetration depth, higher damage threshold, higher image contrast and fewer scattering effects.¹⁰³⁹ Wang *et al.* found that the CsPbBr₃ NCs exhibit strong nonlinear absorption and derived a two-photon absorption (2PA) cross section (σ_2) as high as $\sim 1.2 \times 10^5$ GM (1 GM = 10^{-50} cm⁴ s) at 800 nm for 9-nm-sized CsPbBr₃ NCs.¹⁰¹¹ It is worth mentioning that the 2PA cross section of various dye molecules is in the range of 10–10³ GM.¹⁰⁴⁰ Furthermore, it was demonstrated that these close-packed thin films of CsPbBr₃ NCs possessed low threshold of frequency-upconverted SE pumped by simultaneous two-photon absorption (800 nm, threshold ~ 2.5 mJ cm⁻²) or three-photon absorption (3PA) (1200 nm, threshold ~ 5.2 mJ cm⁻²) (Figure 120e), and the photostability of SE under two-photon pumping was practically favorable. Moreover, $\langle N \rangle$ can be calculated from the equation $\langle N \rangle = f^2 \sigma_2 / \tau$,¹⁰¹¹ where f is the pump fluence (photons cm⁻²) and τ is the pulse line width; the $\langle N \rangle$ at SE threshold is estimated to be ~ 1.2 , which indicates that the SE in perovskite NCs arises from biexciton recombination. Soon after, a two-photon-pumped laser with high stability based on CsPbBr₃ NCs was demonstrated in the work by Xu *et al.*¹⁰²⁰ Figure 120g displays

two-photon fluorescent images of CsPbX₃ perovskite NCs with different halide stoichiometries under 800 and 1064 nm excitation. It is noted that the progress in nonlinear optically pumped SE and lasing from perovskite NCs may offer additional possibilities in the development of next-generation multiphoton imaging techniques.^{7,1011,1041}

Apart from the IHPNs, the OIHP NCs also exhibit SE with fairly low thresholds and the photostability was improved by surface ligand engineering and chemical treatment. In 2017, Protesescu *et al.* synthesized monodisperse, nearly cubic FAPbI₃ and FA_{0.1}Cs_{0.9}PbI₃ with average sizes of 10–15 nm, which extends the emission spectra into the NIR range (e.g., 780 nm for FAPbI₃ NCs).⁶⁹ The SE threshold of 7.5 μ J cm⁻² of FAPbI₃ was among the lowest values of the red to near-IR emitting perovskites (5–10 μ J cm⁻²).^{17,525,1010,1043} Figure 121a,b separately shows the emission spectra of FAPbI₃ and FA_{0.1}Cs_{0.9}PbI₃ NCs films pumped by a pulsed laser with pulse width of 100 fs, indicating ultralow threshold SE.^{69,1044} The integrated PL emission intensity as a function of pump fluence is plotted in Figure 121a,b, separately. It is highlighted that surface engineering can serve as an effective strategy to improve the stability where the active media are made of organic–inorganic hybrid components.^{1037,1044} The robust FAPbI₃ NCs exhibiting low-threshold SE manifest improved ambient thermodynamic and chemical stability over pristine CsPbI₃ analogues,^{1045,1046} making them suitable for light-

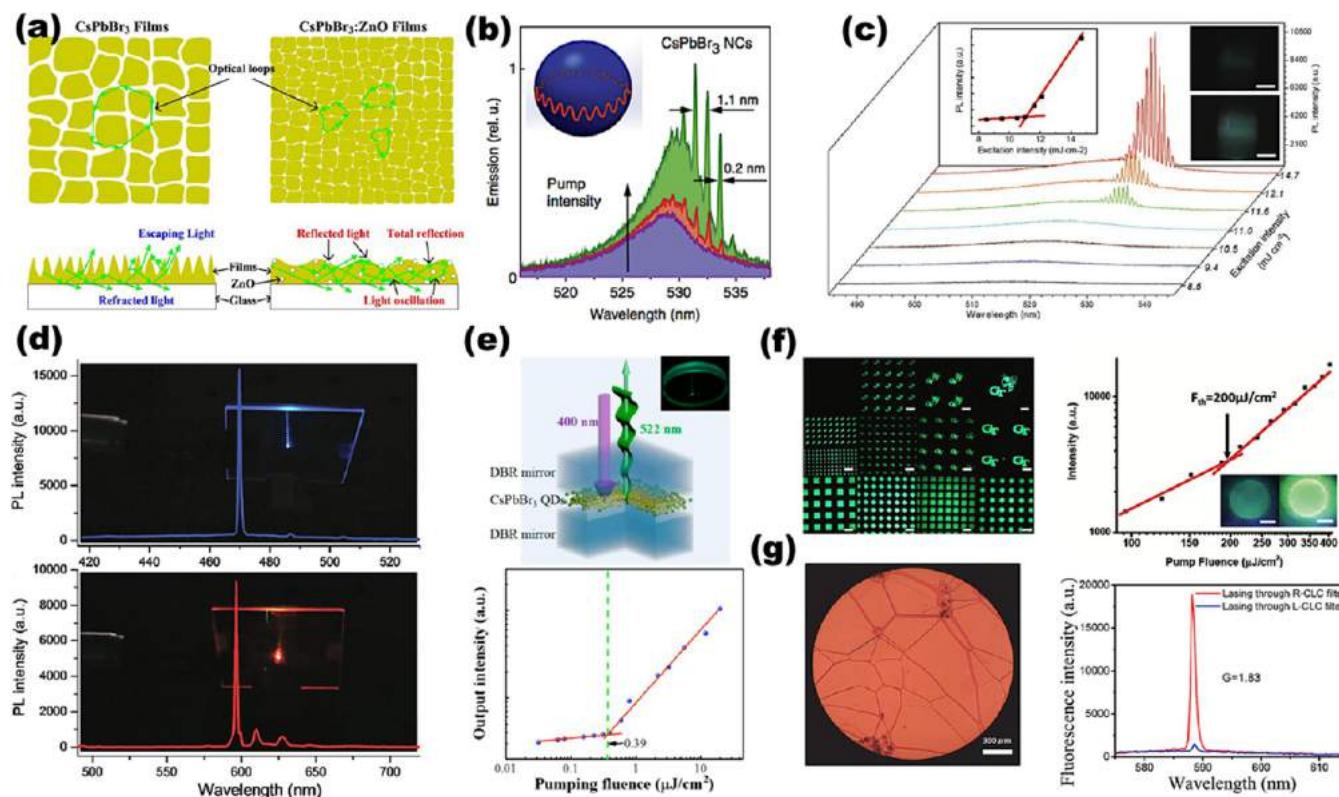


Figure 122. Different laser devices based on perovskite NCs. (a) Shortened optical loops and increased light oscillation in the perovskite $\text{CsPbBr}_3\text{:ZnO}$ films for random lasing. Reproduced with permission from ref 1049. 2017 Elsevier Ltd. (b) WGM lasing in a microsphere resonator of 15 mm in diameter, covered by a film of CsPbBr_3 nanocrystals. Reprinted with permission under a Creative Commons CC BY license from ref 1010. Copyright 2015 The Authors. (c) WGM lasing from CsPbBr_3 nanocrystals infiltrated into a capillary tube with inner diameter of $\approx 50 \mu\text{m}$. Reproduced with permission from ref 28. Copyright 2015 John Wiley & Sons, Inc. (d) Blue and red lasing spectra of VCSELs from $\text{CsPb}(\text{Br/Cl})_3$ and $\text{CsPb}(\text{I/Br})_3$ IHPNs under pump intensity of 38.2 and $30.5 \mu\text{J cm}^{-2}$, respectively. Reproduced with permission from ref 1014. Copyright 2017 John Wiley & Sons, Inc. (e) Schematic of CsPbBr_3 NC-based VCSELs setup with ultralow lasing threshold ($0.39 \mu\text{J cm}^{-2}$). Reproduced from ref 1051. Copyright 2017 American Chemical Society. (f) Different arrays of CsPbBr_3 nanocrystals patterns and lasing in arrays of microdisk lasers. Reproduced with permission from ref 696. Copyright 2018 John Wiley & Sons, Inc. (g) Single mode lasing action in CsSnI_3 -doped with CLC cavities. Reproduced from ref 582. Copyright 2018 American Chemical Society.

emitting applications, including lasers in the red spectral region. Also, it was demonstrated that FAPbBr_3 NCs show low SE threshold and temperature insensitive SE under both one- and two-photon pumping, benefiting from large two-photon absorption coefficient (0.76 cm GW^{-1}) and high optical net gain (480 cm^{-1}).¹⁰⁴⁷ The WGM lasing from these FAPbBr_3 NCs under two-photon excitation was achieved by inserting FAPbBr_3 NCs into a microresonator.¹⁰⁴⁷ In 2017, Veldhuis *et al.*¹⁰⁴² reported the high-yield synthesis of luminescent MAPbBr_3 NCs through direct precipitation of the chemical precursors in a benzyl alcohol (BnOH)–toluene phase, where BnOH can steer the passivating ligands and maintain the ligand binding motifs on the NCs surface, resulting in improved structural stability and optoelectronic properties. They revealed ultralow SE thresholds ($13.9 \pm 1.3 \mu\text{J cm}^{-2}$ under one-photon (400 nm) absorption, Figure 121c; $569.7 \pm 6 \mu\text{J cm}^{-2}$ at two-photon (800 nm) absorption, Figure 121d), high stability under ambient storage and measurement conditions (Figure 121e), as well as outstanding optical modal gain coefficient (520 cm^{-1}) through the detailed ultrafast spectroscopic studies.

Laser Devices Developed From MHPs. A suitable feedback mechanism combined with a gain material is the key to realize a laser device, in which the light can be amplified in certain

resonating frequencies.^{1036,1037} In this regard, a variety of high-quality optical resonators were employed aiming at realizing desirable coherent light output based on perovskite NCs.

Random lasers are the simplest laser configuration where the optical feedback is offered by the constructive interference of the scattered light in a disordered system.^{1036,1048} In 2017, random lasing was demonstrated in the perovskite $\text{CsPbBr}_3\text{:ZnO}$ films. The ZnO nanoparticles were found to be able to improve the lasing performance thanks to the shortened optical loops and increased light oscillation as shown in Figure 122a. In this way, the SE thresholds of $\text{CsPbBr}_3\text{:ZnO}$ films were significantly reduced under both 1PA and 2PA.¹⁰⁴⁹ Leveraging on the similar strategy, ultralow threshold random lasing was achieved by depositing MAPbBr_3 NCs on a heterostructure of 3D graphene-sheathed SiC nanowalls.¹⁰⁵⁰ Strong scattering of emitted photons by leachy vertical graphene networks provide the effective optical feedback to achieve random lasing. Moreover, the lasing threshold can be further lowered by the combined effect of the improved scattering cross section and plasmonic field enhancement of extra Ag/SiO_2 particles.

Silica microspheres can naturally serve as WGM cavities. Yakunin *et al.*¹⁰¹⁰ coated the IHPNs onto silica spheres to construct a WGM microlaser (Figure 122b, inset), in which

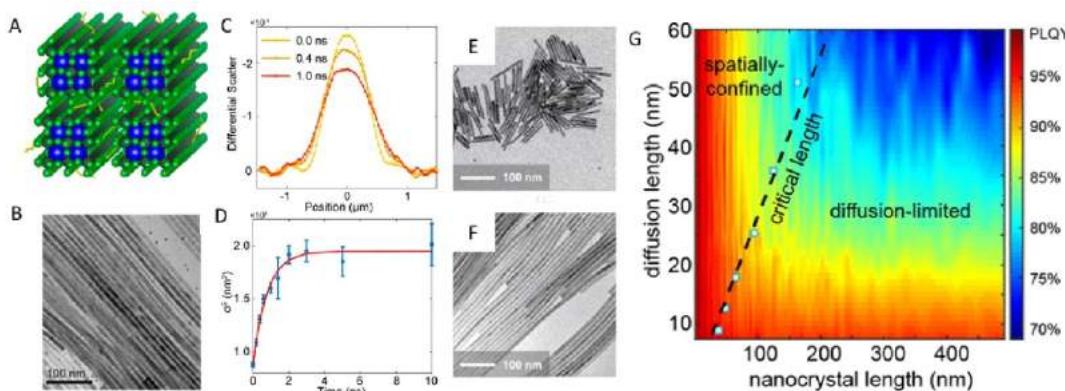


Figure 123. (A) Schematic diagram and (B) SEM image of perovskite nanowire bundles. (C,D) Diffusion profile of energy along the longitudinal axis of the nanowires. Reproduced from ref 1058. Copyright 2020 American Chemical Society. (E,F) TEM images of CsPbBr_3 nanowires with different aspect ratios. (G) 2D counter plot as an illustration of the optical scaling law of PLQY as a function of NC length in both the spatially confined regime and the diffusion-limited regime. Reproduced from ref 239. Copyright 2020 American Chemical Society.

the light propagation was total internally reflected around the circular cavity edges.^{1010,1036} WGM lasing could also be developed by infiltrating the gain media into a capillary tube.^{1052,1053} In a similar way, Wang *et al.* coated a thin film of CsPbBr_3 NCs onto the inner wall of a capillary tube to realize high-performance WGM lasers with a quality factor (Q-factor) of ~ 2000 (Figure 122c).²⁸ The occurrence of evenly spaced spikes and super-linear increase of the integrated PL intensity *versus* pump fluence (inset in Figure 122c, left) confirmed the development of lasing action, and the longitudinal optical modes could be well-assigned according to the WGM model.^{1053–1055} Recently, by embedding a CsPbBr_3 – SiO_2 spheres into a microtubule, the frequency up-converted WGM lasing over 140 min with a low lasing threshold of $430 \mu\text{J cm}^{-2}$ has been successfully achieved under two-photon excitation. Combining the effects of natural microring resonator of SiO_2 and high gain of CsPbBr_3 NCs provides a promising strategy to realize frequency up-converted lasing devices with low threshold.¹⁰⁵⁶

A DFB laser is made of a grating structure in which the active region contains a periodically varied refractive index distribution. The grating provides optical feedback for a wavelength satisfying the Bragg condition.¹⁰³⁷ In 2016, DFB lasers based on MAPbI_3 perovskites with threshold at optical pump intensities of 5 kW cm^{-2} for durations up to ~ 25 ns at repetition rates exceeding 2 MHz were reported. It highlighted that using the short pulse drive would be an effective strategy to reduce the threshold in a perovskite NC-based laser diode.¹⁰²¹ After that, highly green luminescent MAPbBr_3 perovskite film composed of large NCs were used to produce stable DFB lasers at 550 nm with a low threshold of $6 \mu\text{J cm}^{-2}$. These DFB lasers were able to support multiple polarizations and could be switched between transverse magnetic and transverse electric mode operation through tuning of the distributed feedback grating period.¹⁰²²

Additionally, VCSELs, basically constructed by inserting an active layer into two parallel reflecting mirrors, have been demonstrated based on perovskite NCs. In 2017, Wang *et al.*¹⁰¹⁴ sandwiched the CsPbX_3 NCs between two distributed Bragg mirrors (DBRs) to achieve high-performance VCSELs. These lasers showed low threshold ($9 \mu\text{J cm}^{-2}$), directional output (beam divergence of $\sim 3.6^\circ$), and favorable stability. Blue-emitting $\text{CsPb}(\text{Br/Cl})_3$ IHPNs and red-emitting $\text{CsPb}(\text{I/Br})_3$ IHPNs were similarly inserted into the DBR resonators to

obtain the VCSELs across the full visible spectral range (Figure 122d). In the same year, VCSELs based on CsPbBr_3 NCs with ultralow lasing threshold ($0.39 \mu\text{J cm}^{-2}$, Figure 122e) was also reported. The schematic of the CsPbBr_3 NCs based VCSELs is shown in Figure 122e. These VCSELs exhibited stable device operation over 5 h or 1.8×10^7 optical excitation pulses at ambient condition, demonstrating the potential in practical coherent light-emitting applications.¹⁰⁵¹

Moreover, duplicatable and scalable microlaser arrays have been realized from CsPbX_3 NCs relying on an orthogonal lithography approach, which is promising for integrated photonic applications.⁶⁹⁶ For example, Lin *et al.* fabricated large-area high-resolution arrays of microdisk lasers and multicolor (binary and ternary emission) pixels (Figure 122f).⁶⁹⁶ The reported orthogonal lithography method preserved the high optical gain performance of CsPbBr_3 NCs, which was the key to achieve the WGM lasing.^{696,1026}

Dynamically tunable lasers have been realized by doping CsSnI_3 NCs into cholesteric liquid crystal (CLC) reflectors. (Figure 122g).⁵⁸² A similar approach was employed by Stranks *et al.*¹⁰⁵⁷ to obtain robust lasing under nanosecond pumping at 532 nm (a minimum threshold of $7.6 \mu\text{J cm}^{-2}$). A thin CLC film ($\sim 7 \mu\text{m}$) coupled with a metal back-reflecter was adopted to construct the cavity. The use of flexible CLC reflectors provides a pivotal step toward “mirror-less” single-mode lasers on flexible substrates, which could be exploited in applications such as flexible displays and military identification.

MHP Nanowire Lasers. Despite the fact that the carrier dynamics in perovskite NCs has been extensively studied in 0D quantum dots systems, studies on the 1D geometry of perovskite NWs also demonstrate an important role on the modification of electronic structure, carrier trapping, and exciton decay mechanisms. Carrier diffusion in one-dimensional CsPbBr_3 NWs with 10 nm lateral widths were directly visualized from stroboSCAT (stroboscopic interferometric scattering microscopy) measurements (Figure 123A–D).¹⁰⁵⁸ The rapidly diffusing excitons encounter less trap densities along the NWs. The qualitative study using ultrafast transient microscopy showed the anisotropy splitting of the band-edge exciton in NWs due to dielectric confinement in one dimension.¹⁰⁵⁸

To demonstrate the charge carrier behaviors in a more controllable system, high-quality, single-crystalline 1D CsPbX_3 NWs with aspect ratios varying from 1 to 1000 were used to

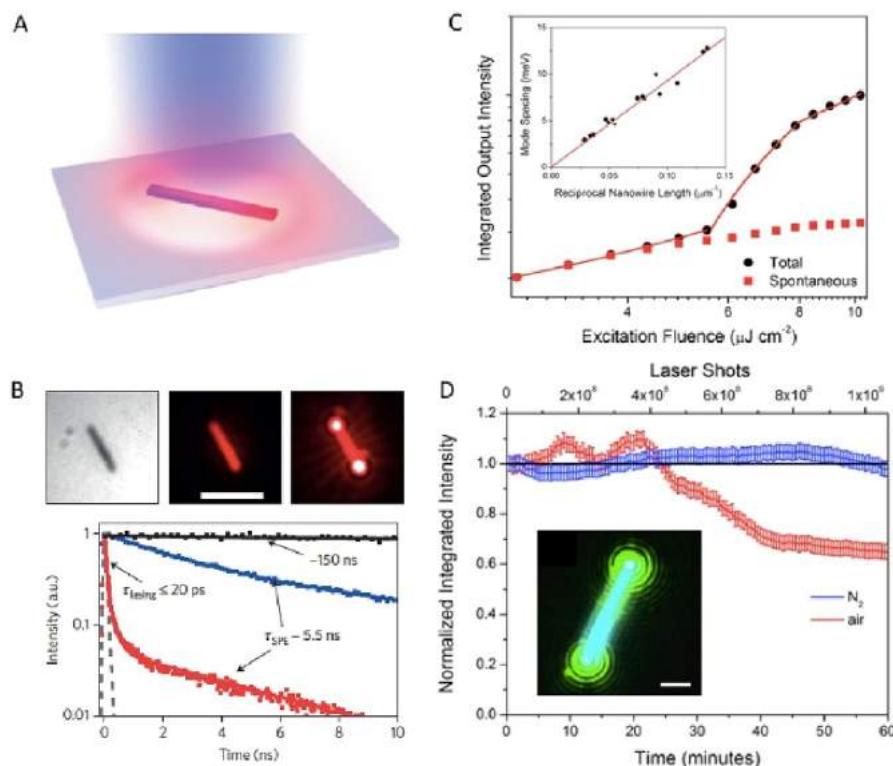


Figure 124. (A) Schematic diagram of perovskite nanowire pumped by a laser. (B) Optical images of a single nanowire with and without laser excitation and corresponding transient PL decay kinetics at certain excitation intensity. Reproduced with permission from ref 34. Copyright 2015 Nature Publishing Group. (C) Integrated output intensity from CsPbBr_3 nanowire as a function of increasing excitation fluence. (D) Stability test of lasing from CsPbBr_3 nanowire in both air and N_2 environment. Reproduced with permission under a Creative Commons CC BY license from ref 244. Copyright 2016 National Academy of Sciences of the United States of America.

construct a model platform to investigate the optical scaling laws of NCs (Figure 123E–G).²³⁹ NW surface ligands with tunable Lewis acidity offer control over the nonradiative rate of the perovskite NWs. Steady-state PLQY and time-resolved PL lifetime measurements have yielded valuable information on the impact of NWs aspect ratio on excitonic dynamics within the wire. The scaling laws derived from this model system are not only a phenomenological observation but unraveled the carrier dynamics of these microscopic systems in a quantitative and interpretable manner. Monte Carlo simulations with an exciton-diffusion–defect-encounter random walk model extracted an exciton diffusivity of $0.4 \text{ cm}^2/\text{s}$, and together with the scaling behaviors, revealed materials dimensionality as a hidden constraint on the carrier recombination kinetics. In addition, Janker *et al.* employed the spatiotemporal dynamics of electrons and holes in aligned CsPbI_3 NW bundles using acousto-optoelectric spectroscopy.¹⁰⁵⁹

The carrier dynamics studies of perovskite NWs mentioned above paved the way for the rationally designed NW laser systems. NW lasers are ideal candidates for miniaturized light sources, providing both the optical gain medium and the resonant laser cavity that can potentially allow their facile integration into circuits. The perovskite NWs that were synthesized from colloidal methods are too thin to effectively support the photonic lasing modes. A low-temperature, solution-phase growth of single-crystalline CsPbX_3 NWs with a few hundred nm in width and micron length scale led to the Fabry-Pérot mode lasing behavior with a low lasing threshold, high maximum quality factor, and the wavelength tunability from blue to near-IR regions of the visible spectrum (Figure

124).^{34,242,244,1060,1061} The confined exciton–polaritons in perovskite NWs and the composition-dependent Rabi splitting has been studied using high-quality in-plane aligned CsPbX_3 ($X = \text{Cl}, \text{Br}, \text{I}$) NWs that were grown on the M-plane sapphire substrates.¹⁰⁶² The corresponding energy–wavevector dispersion relation of the lasing mode well agreed with the exciton–polariton model, and the Rabi splitting was extracted as $\sim 210 \pm 13$, 146 ± 9 , and 103 ± 5 meV in CsPbCl_3 , CsPbBr_3 , and CsPbI_3 NWs. Moreover, the lasing from CsPbBr_3 NWs has been maintained for over 1 h of constant pulsed excitation in both nitrogen and ambient atmospheres (Figure 124D).²⁴⁴ This represents significant stability of inorganic perovskite NWs and demonstrates the viability of the robust, all inorganic compositions for photonic integrated circuits that require highly stable miniaturized light sources. In addition to the inorganic perovskite NWs for lasing, organic–inorganic hybrid $\text{CH}_3\text{NH}_3\text{PbX}_3$ NWs have been grown from vapor-phase synthesis and equally show excellent optical properties with adequate gain and efficient optical feedback.¹⁰⁶³ The surface plasmon effect in $\text{CH}_3\text{NH}_3\text{PbBr}_3/\text{SiO}_2/\text{Ag}$ cavity can further enhance the strong exciton–photon interactions in perovskite NWs.¹⁰⁶⁴ The exciton–photon coupling strength can be enhanced by $\sim 35\%$, and this is attributed to the localized excitation field redistribution from surface plasmon effect.

The origin of the lasing in halide perovskite NWs is still a controversial topic. In addition to the lasing mechanism involving exciton–polaritons as mentioned above, Schlaus, *et al.*, have proposed that under the pulsed excitation density, the excitation power would exceed the exciton Mott density, and

as a result, lasing in CsPbBr_3 NWs was originated from the stimulated emission of a nondegenerate electron–hole plasma rather than exciton–polaritons.¹⁰⁶⁵ The changes in laser gain profile and refractive index that lead to the lasing mode distribution of NWs strongly depend on excitation density and pulse duration time. In particular, the high intrinsic PL quantum efficiency is crucial for advancing their application as light-emitting sources. It has been demonstrated that the quantum efficiency of single-crystalline CsPbBr_3 NWs can be improved by 3 orders of magnitude upon exposure to oxygen molecules.²⁴⁹ Oxygen can passivate the perovskite surface defects originated from lead-rich surface, therefore it greatly reduces the nonradiative recombination rate.

Summary and Future Outlook for MHP Lasers. Perovskite NCs, including organic–inorganic hybrid and all-inorganic perovskite NCs, are emerging as a contemporary class of cost-effective and wavelength-tunable lasing materials. Although tremendous progress has been made in developing solution-processed lasers from perovskite NCs, especially in terms of understanding the fundamental physics and improving the device performance, there remain challenges with regard to developing practical and commercially available lasers utilizing the perovskite NCs. Firstly, these perovskite NCs are severely affected by chemical and environmental factors (e.g., oxygen, moisture, heat, and continuous light illumination) instabilities.^{462,1066,1067} Li *et al.* developed an amination-mediated nucleation strategy and demonstrated significantly improved SE stability of perovskite NCs.¹⁰⁶⁸ In another case, Yuan *et al.* fabricated CsPbBr_3 NCs in a glass matrix *in situ* crystallization synthesis, which not only protected the NCs from the ambient conditions, but also hindered their aggregation.⁴⁶⁴ In 2017, Wang *et al.* demonstrated the insertion of CsPbBr_3 NCs into a wider-band-gap Cs_4PbBr_6 matrix through a low-temperature solution-phase synthesis method. It was found that the thermal stability of IHPNs is enhanced, and robust high-temperature perovskite lasers could be realized.³⁶⁴ However, most of the strategies are only applicable for the pure, green emitting CsPbBr_3 NCs, while the stability of blue-emitting and red-emitting perovskite NCs is lagging behind. Secondly, most of the progress made on perovskite NCs lasers^{168,1069–1071} has focused on lead-containing compounds, which are toxic and their use may be restricted in the future. As a result, studying nontoxic NCs and developing heavy metal-free perovskite NCs for laser media will probably be an irreversible trend.¹⁰⁷² For example, air-stable lead-free double perovskites NCs with chemical formula $\text{A}_2\text{MM}'\text{X}_6$, where A is a monovalent cation (Cs^+ , CH_3NH_3^+ , etc.), M is also a monovalent cation (Ag^+ , Na^+ , etc.), M' is a trivalent cation (In^{3+} , Bi^{3+} , Sb^{3+} , etc.), and X is the halogen anion (Cl^- , Br^- , I^-) have been recently synthesized (see dedicated sections in this review on **NANOCRYSTALS OF LEAD-FREE PEROVSKITE-INSPIRED MATERIALS**), and they could be promising for lead-free perovskite lasers in the near future.⁵⁷¹ Thirdly, to date, only optically pumped lasing has been demonstrated in perovskite NCs, whereas electrical pumping is more practically desired.^{1071,1072} Despite significant progress in optically pumped lasers and electrically driven light-emitting diodes has been demonstrated, there is still a long way to go before realizing electrically-pumped perovskite NC lasers. In particular, the following issues have to be addressed to achieve lasing in NCs by electrical pumping. First, the Auger recombination generally limits the electrically driven lasing in perovskite NCs because the carriers are injected into perovskite NCs one-by-

one.¹⁰⁷³ Thus, this nonradiative Auger recombination has to be suppressed by electron–hole wave function engineering and other additional strategies. Second, the organic ligands used for the passivation of perovskite NC surfaces generally exhibit poor electrical conductivity, hampering the carrier injection and transport.^{1010,1070} Therefore, it is imperative to find ways to achieve efficient injection of charge carriers into the perovskite NC layer. The methods include the modification of the NC surface and the reduction of the thickness of the emitting layer.

Light-Emitting Devices. Light-emitting diodes based on lead-halide perovskites emerged more than a decade ago. However, there was no electroluminescence reported at that time because of the weak light emission from LHPs.^{1074–1076} However, in the past few years, there have been significant developments and LHPs have returned to the spotlight, not only as highly efficient photon absorbers in solar cells, but also as efficient photon emitters in LEDs.^{8,31,1077} Interestingly, the external quantum efficiencies of LHP-LEDs reached the same level as organic LEDs and colloidal cadmium selenide QD LEDs of over 20% in just 5 years.^{404,1078,1079} Generally, the whole LHP-LED with a total thickness of hundreds of nanometers is deposited onto a transparent substrate coated with an indium tin oxide electrode, and functional films are also required for facilitating charge carrier injection into the LHP layer from external electrodes.^{31,404,1078,1079} Because the LHP emitter and other functional layers are deposited by solution processing, the device structures of most LHP-LEDs are simple.^{31,404,1078,1079} By changing the halide anion from chloride to iodide, the emission wavelength of LHPs can be tuned across the whole visible range (refer to **Composition Control by Ion Exchange and Suppression of Exchange** section).^{14,53,80,1080,1081} Moreover, nanostructured emitters are effective for confining charge carriers in the LHP layer and achieve highly efficient radiative recombination. These nanostructured emitters include 3D NCs, quasi-2D nanoplatelets, and multilayer quantum wells.^{22,216,385,901,1062,1078,1082} Apart from high EQEs, LHP-LEDs achieve narrow emission peaks with high-color purity.^{53,78,404,1083} LHP-LEDs are therefore a natural candidate for potential applications in full-color information displays. So far, bromide- and iodide-based green and near-infrared LHP-LEDs have achieved record EQEs of over 20%. However, the development of blue LHP-LEDs lags behind.^{385,404,1078,1079,1084} The synthesis of a wide variety of LHP emitters and their deposition in films can be conducted simply and quickly, even in ambient atmosphere, which is another advantage compared to their counterparts, such as CdSe QDs.^{14,52,78,1083} As a soft semiconductor emitter, the similarity in the processing LHPs and OLEDs/QD-LEDs suggests that LHPs may be compatible with the booming OLED/QD-LED industry.^{1062,1078,1079} However, LHP emitters and the resulting LEDs are still limited by the toxicity of the lead ions and rapid degradation under operation condition, and efforts to develop lead-free alternatives are discussed in the earlier section on **NANOCRYSTALS OF LEAD-FREE PEROVSKITE-INSPIRED MATERIALS**.^{112,469,885,1080,499,1085–1088} Details of the fundamental properties of LHPs (e.g., band gap tunability, defect tolerance and carrier dynamics) are covered in previous sections, particularly the section on **OPTICAL PROPERTIES**.

Classification of Perovskite Light Emitters. Although the initial perovskite LEDs to operate at room temperature used

bulk 3D perovskite thin films, the EQEs reached up to only ~1%.³¹ An important challenge was the low exciton binding energy of a few meV in the films,⁸⁹⁴ necessitating the spatial confinement of charges to increase the fraction of injected carriers that radiatively recombine.¹⁰⁸⁹ While this was initially achieved by creating a quantum well (by sandwiching the emitter between two injectors that each block one of the carriers),³¹ a more effective strategy was to create a multi-quantum-well structure through thin films comprising mixtures of perovskites with different dimensionality (3D, 2D, and quasi-2D).³⁸⁵ This has led to near-infrared perovskite LEDs with >20% EQE.¹⁰⁷⁹ However, controlling the phase-purity and distribution of phases in these multidimensional perovskite thin films remains challenging.¹⁰⁸⁹ An important alternative to thin films for improving the spatial confinement of charge carriers is through nanostructured perovskites. These include colloidal nanocubes, nanoplatelets, NCs embedded in 3D perovskite matrices and perovskite–polymer composites (Figure 125). Nanostructured perovskites have the advantages of higher exciton binding energy, band gap tunability, and the ability to passivate the surfaces to achieve high PLQYs near-unity.⁵² Details of the synthesis and optical properties of nanocubes and NPs are given above, while 0D nonperovskites and NCs embedded in these nonperovskites are discussed in other sections of this review. The discussion below focuses on the application of these materials in LEDs.

Nanocrystal Emitters. Efficient performance has been achieved in perovskite NC LEDs emitting across the entire visible wavelength range. The morphology of the most widely explored LHP NCs is shown in Figure 126a. Two critical strategies that have enabled this result are surface passivation and the use of dopants.

An important source of nonradiative recombination is due to uncoordinated Pb^{2+} at the surface of NCs. In red-emitting CsPbI_3 NCs, the uncoordinated Pb^{2+} ions were passivated by introducing excess iodine to the surface. This was achieved using excess trimethylsilyl iodide as the iodine source during synthesis, which resulted in the surface I/Pb ratio reaching 4.4. Through surface passivation, the PLQY of the colloidal NCs in solution approached unity, and the device reached 1.8% EQE.¹⁶⁸ Surface passivation can also be achieved post-synthesis. For example, Pan *et al.*¹⁷² introduced 2,2'-iminodibenzonic acid to CsPbI_3 NCs, leading to a peak EQE increase from 2.26% to 5.02%. The improvement in performance was attributed to the bidentate ligands binding firmly to the PbI_2 -rich surface of the NCs and reducing the density of surface traps. Potassium halides have also been found to be effective surface passivation agents and were used by Yang *et al.* to passivate the surface of $\text{CsPbI}_{3-x}\text{Br}_x$ NCs to suppress phase separation into iodide- and bromide-rich regions, and this stabilized the PL spectra over time, as shown in Figure 126b. In doing so, they achieved electroluminescence at 637 nm wavelength, which is required for pure-red emission for displays, and increased the EQE from 1.89% (pristine NCs) to 3.55% (KBr-passivated NCs) as shown in Figure 126c.¹⁰⁹²

An important challenge with CsPbI_3 is that the cubic perovskite phase (the α -phase) is metastable at room temperature, due to the small size of the Cs^+ cation, which leads to the Goldschmidt tolerance factor being below the range for cubic perovskites (refer to the beginning of the review).⁵¹ The room-temperature orthorhombic phase has a wider band gap and undesirable optoelectronic properties.¹⁰⁹³

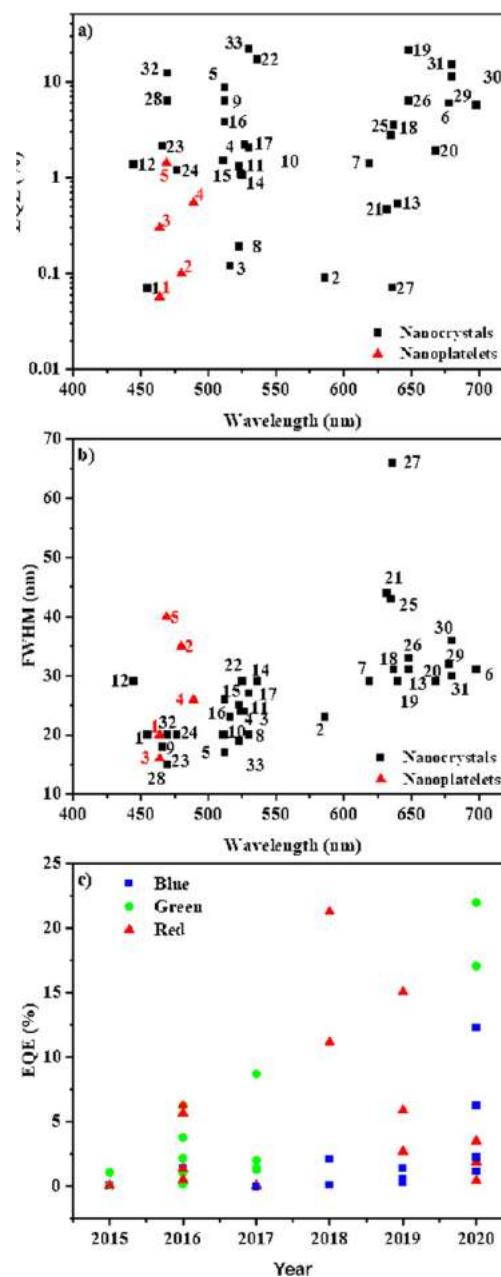


Figure 125. (a) EQE and (b) PL fwhm vs emission wavelength for different emitters and structures. The number labeled in the figure matches the label number in Table 3, and the corresponding references are also shown in Table 3. (c) Development of red, green, and blue PeLEDs over time.

An approach to stabilize the α -phase at room temperature is to partially replace Pb^{2+} cations with smaller cations (e.g., Sr^{2+} , Ag^+ , and Zn^{2+}), in order to increase the tolerance factor. LEDs made from these perovskites emitted at 678–690 nm, with EQEs ranging from 5.92% (Sr doping) to 15.1% (Zn doping).^{626,627,631} Another successful approach was iodide anion-exchange in CsPbBr_3 NCs. For example, Mathews and co-workers used FAI in water as the iodide source for ion exchange. Water was used because it is not miscible with the toluene solvent for the colloidal CsPbBr_3 quantum dots, therefore preventing ligand desorption. By tuning the concentration of FAI in the aqueous solution, either mixed Br/I or pure I-based NCs were achieved, with EL wavelengths

Table 3. External Quantum Efficiency and Full Width at Half-Maximum of Electroluminescence of Perovskite Nanocrystal and Nanoplatelet Light-Emitting Diodes

labels in Figure 125	emitting materials	EL peak center (nm)	EQE (%)	fwhm (nm)	ref
1	CsPbBr _x Cl _{3-x}	455	0.07	20	27
2	CsPbBr _x I _{3-x}	586	0.09	23	27
3	CsPbBr ₃	516	0.12	23	27
4	CsPbBr ₃ /CsPb ₂ Br ₅	527	2.21	24	1066
5	CsPbBr ₃	512	8.73	17	190
6	CsPbI ₃	698	5.7	31	1067
7	CsPbBr _{0.75} I _{2.25}	619	1.4	29	1067
8	CsPbBr ₃	523	0.19	19	1067
9	CsPbBr ₃	512	6.27	20	184
10	CsPbBr ₃ :Mn ²⁺	511	1.49	20	621
11	MA _{0.8} Cs _{0.2} PbBr ₃	523	1.3	25	1090
12	MAPb(BrCl) ₃	445	1.37	29	1091
13	MAPbI ₃	640	0.53	29	1091
14	MAPbBr ₃	525	1.06	29	1091
15	MAPbBr ₃	524	1.1	24	141
16	MAPbBr ₃	512	3.8	26	1083
17	FAPbBr ₃	530	2.05	27	403
18	CsPbI _{3-x} Br _x	637	3.55	31	1092
19	CsPbBr _{0.6} I _{2.4}	648	21.3	31	1078
20	CsPbI ₃	668	1.9	29	1093
21	CsPbBr _x I _{3-x}	632	0.47	44	1093
22	FAPbBr ₃	536	17.1	29	1094
23	CsMn _y Pb _{1-y} Br _x I _{1-x}	466	2.12	17.9	1095
24	CsPbBr _x Cl _{3-x}	477	1.19	20	1096
25	MAPbBr _x I _{3-x}	635	2.75	43	1097
26	CsPbBr _x I _{3-x}	648	6.3	33	1098
27	CsPbBr _x I _{3-x}	636	0.071	66	1099
28	CsPbBr _x Cl _{3-x}	470	6.3	15	1100
29	Sr-CsPbI ₃	678	5.92	32	627
30	Ag-CsPbI ₃	680	11.2	36	631
31	CsPb _{0.64} Zn _{0.36} I ₃	680	15.1	30	626
32	CsPbBr ₃	470	12.3	20	1101
33	CsPbBr ₃	530	22	20	1101
1	CsPbBr ₃ NPL	464	0.057	20	60
2	CsPbBr ₃ NPL	480	0.1	35	216
3	CsPbBr ₃ NPL	464	0.3	16	1102
4	CsPbBr ₃ NPL	489	0.55	26	1102
5	CsPbBr ₃ NPL	469	1.42	40	1103

ranging from 630 to 670 nm (pure iodide) and high PLQYs >74%. However, the EQEs only reached up to 1.9% for CsPbI₃ NCs.¹⁰⁹³ Chiba *et al.*¹⁰⁷⁸ achieved much higher EQEs, reaching 21.3%, through anion exchange using iodide-containing ligands. Starting with CsPbBr₃ NCs, oleylammonium iodide (OAM-I) was used for halide exchange to form CsPbI₃ by adding the ligand to the colloidal solution. In this halide-exchange process, the surface anion vacancy concentration was significantly reduced from a starting Br/Pb ratio of 2.78 to a final I/Pb ratio of 3.00. This, in part, accounts for the PLQY increase from 38% for CsPbBr₃ to 80% for CsPbI₃. Although the EQE of the CsPbI₃ LEDs matched their bulk thin film counterparts, the device stability was limited, with the performance halving after only 5 min at 1.25 mA cm⁻² current density.¹⁰⁷⁸

Surface engineering has also been important for improving the performance of green emitters (510–530 nm wavelength). Successful strategies include: (1) eliminating labile OLA

(oleylamine) from the synthesis (EQE = 0.32%),³⁴⁶ (2) treating NCs with ammonium thiocyanate (EQE = 1.2%),¹¹⁰⁴ (3) employing octylphosphonic acid post-synthesis (EQE = 7.74%),¹¹⁰⁵ (4) using didodecyldimethylammonium ligand during synthesis (EQE = 9.80%),¹¹⁰⁶ and (5) triple ligand–surface treatment (EQE = 11.6%).¹¹⁰⁷ Combining these organic ligands with inorganic passivation agents has also been shown to be effective in improving EQE. The addition of ZnBr₂ to DDA-Br-capped NCs resulted in the improvement of the EQE of the green LEDs from 10.7 to 16.48%.³⁹⁶ Introducing excess FABr to the precursor solution was also found to be effective, with PLQYs increasing from 62% to 74% in films, and device EQEs increasing from 1.5 to 17.1%, as the FABr/PbBr₂ molar ratio was increased from 1:1 to 2.2:1.¹¹⁰⁸ XPS measurements indicated that there was a reduction in the concentration of bromide and formamidinium vacancies, which may be due to these being filled by the excess FABr. There was also a lower surface ligand density, which may have resulted in improved charge transport between the NCs. The operational stability was also improved from 52 s (control (FABr/PbBr₂ molar ratio 1:1)) to 1080 s (FABr/PbBr₂ molar ratio 2.2:1), due to the suppression of nonradiative recombination as the excess FABr passivated the surface defects. However, it was found that this was not due to any improvements in thermal stability, which was found to be unaffected by the addition of FABr from thermogravimetric analysis.¹¹⁰⁸ Indeed, Dong *et al.*¹¹⁰¹ found that a limitation of ligand exchange is that the process results in the removal of surface bromide anions, which results in lower PLQYs. They showed that this could be overcome by mixing the NC solution with a saturated solution of isopropylammonium bromide in DMF or NaBr in DMF after multiple reprecipitation steps to heal the surface bromide vacancies. As a result, their 4 and 7 nm CsPbBr₃ NCs exhibited near-unity PLQYs after ligand exchange, resulting in blue LEDs with 12.2% EQE (480 nm wavelength).¹¹⁰¹ Beyond these surface treatments, Zheng *et al.* decorate nickel oxide on the CsPbBr₃ NC surface through adsorption and a sequential oxidation treatment. This resulted in EQE increasing from 0.7 to 16.8% with a drop in turn-on voltage from 5.6 to 2.8 V.¹¹⁰⁹

There has also been increased recent focus on blue-emitting perovskites: it is a fact that the EQEs of these devices currently limit the development of perovskite-based displays and solid-state white lighting. A key challenge is the low PLQYs of Cl-based perovskite emitters. Recent efforts to address this limitation include passivation with K⁺, Cl⁻ (from CuCl₂), Ni²⁺, and Mn²⁺ ions.^{782,1095,1096} Yang *et al.*¹⁰⁹⁶ recognized that a challenge with using oleic acid and oleylamine (the most common ligands) in the synthesis of perovskite NCs is that the protonation process between the acid and amine (*i.e.*, the surface-bound ammonium ion giving back the proton to the surface-bound carboxylate ion) can result in ligand desorption and the formation of surface defects. The introduction of K⁺ (through K₂CO₃) was found to passivate surface defects and also reduce the density of organic ligands required on the surface (as found from Fourier transform infrared spectroscopy), which improved charge transport between NCs in films. It is thought that K⁺ bound to halide ions on the NC surface can passivate dangling bonds. As a result, the PLQY of the colloidal NCs increased from 9.50% (no K⁺) to 38.4% with 8% K⁺, which correlated with increases in the EQE from 0.23% (no K⁺) to 0.82% (8% K⁺).¹⁰⁹⁶ However, the highest EQE was achieved with 4% K⁺ (1.19% EQE) due to improved surface

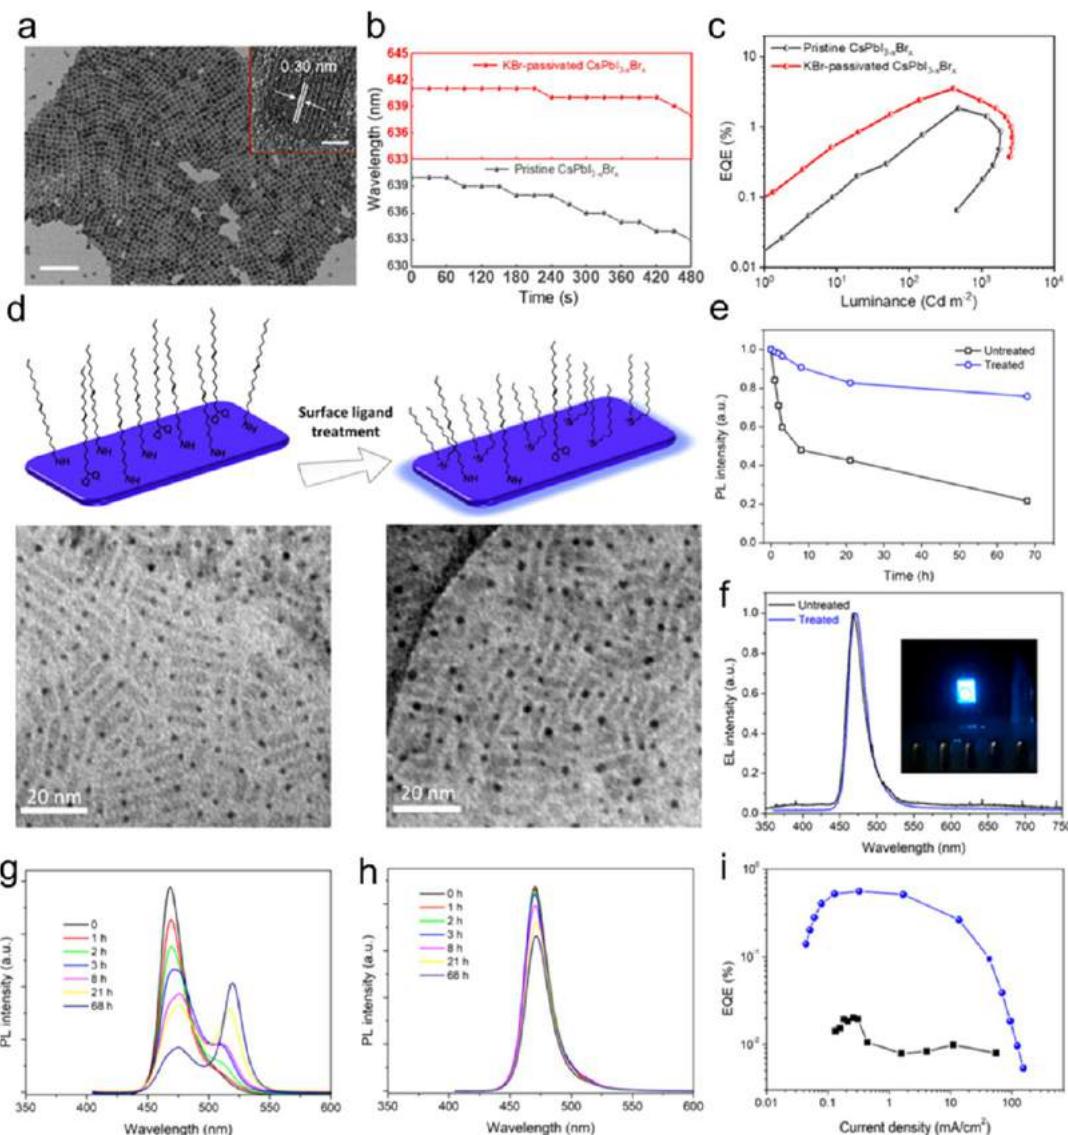


Figure 126. (a) TEM image of KBr-passivated $\text{CsPbI}_{3-x}\text{Br}_x$ NCs. The inset shows the corresponding HRTEM image. Scale bars: 100 and 5 nm. (b) PL peak position as a function of irradiation time for pristine and KBr-passivated $\text{CsPbBr}_{3-x}\text{I}_x$ NC films. The ensemble films were continuously excited by a laser emitting at 365 nm with a power density of 100 mW cm^{-2} . (c) EQEs of LEDs based on prepared pristine and KBr-passivated $\text{CsPbI}_{3-x}\text{Br}_x$ NCs at different luminance. Panels a–c are reprinted from ref 1092. Copyright 2020 American Chemical Society. (d) TEM images of untreated and treated CsPbBr_3 NPs. (e) Remnant PL intensity of treated and untreated NPs. (f) EL spectra of the untreated and treated CsPbBr_3 NPI-based LEDs. Inset: Photograph of a working treated CsPbBr_3 NPI-based LED at a driving voltage of 5 V. Recorded PL spectra of (g) untreated and (h) treated CsPbBr_3 NPI/toluene solutions. (i) External quantum efficiency–current density curves of the untreated and treated CsPbBr_3 NPI-based LEDs. Panels d–i are reprinted from ref 1103. Copyright 2019 American Chemical Society.

morphology, for which the emission wavelength was 476 nm.¹⁰⁹⁶ With surface passivation, the LT_{50} also improved by 2.6 times up to 4.5 min with an applied bias of 4 V. Further improvements in EQE were achieved by replacing the TPBi electron injector with PO-T2T, which has higher mobility that is better matched with the poly-TPD hole injector. By also adding a layer of poly(9-vinylcarbazole) between the poly-TPD and emitter, the EQE reached a peak of 1.96%.¹⁰⁹⁶

De *et al.*⁷⁸² demonstrated that the addition of $\text{CuCl}_2\cdot 2\text{H}_2\text{O}$ to the reaction mixture during the synthesis of CsPbCl_3 by hot injection, led to an increase of the PLQY of CsPbCl_3 NCs from 0.5% (no doping) to 60% (1% Cu doping) at 400 nm wavelength (violet). It was also found that with Cu doping, the NCs became halide-rich rather than halide-deficient, and the

improvement in PLQY is attributed to the reduction in the density of anion vacancies on the surface. Bi *et al.* reported improvements in PLQY in mixed Cl–Br NCs emitting in the 430–460 nm range, which reached 92 and 98%, respectively, after incorporating CuCl_2 . Improvements in the air-stability of the NCs were also seen, but the effect on device performance was not reported.¹¹¹⁰

Hou *et al.*¹⁰⁹⁵ also demonstrated improvements in the PLQY and, consequently, the EQE of blue-emitting $\text{CsPbBr}_{1-x}\text{Cl}_x$ NCs through Mn^{2+} doping (by hot-injection synthesis). The PLQY improved from 9% (no Mn^{2+}) to 28% (with 0.19% Mn^{2+}). This correlated with improvements in the EQE from 0.50 to 2.12% at an emission wavelength of 466 nm. The emission fwhm was also narrow (18 nm). The high-

performance blue LEDs were used to excite red and green perovskite NC down-converters, resulting in CIE coordinates of (0.311, 0.326), close to the values for true white emission. The white-light LED was calculated to have an EQE of 0.25%. Despite the promising device performance, the stability was limited, with the devices degrading within seconds to minutes. Another important challenge is the Mn^{2+} content, which needed to be controlled very carefully. Having Mn^{2+} content above 0.2% resulted in a reduction in the PLQY and a longer-wavelength emission from the Mn^{2+} ion center increasing in intensity significantly.¹⁰⁹⁵ More recently, Zheng *et al.*¹¹⁰⁰ reported the passivation of Cl^- vacancies using *n*-dodecylammonium thiocyanate (DAT). The thiocyanate component is a “pseudo-halide” capable of filling halide vacancies but has the important advantage of not shifting the emission peak (unlike the use of organic halides). DAT was introduced to $CsPb(Br_xCl_{1-x})_3$ quantum dots post-synthesis because the long-chain doedecylammonium component of DAT enabled it to dissolve in toluene, the same solvent of the quantum dots. After post-treatment, the PLQY of the quantum dots increased from 83% (as-synthesized) to 100% (post-treatment), whereas the PL peak remained at the same wavelength (468 nm). The EQE improved from 3.5% (without treatment) to 6.3% (with DAT treatment), with an electroluminescence wavelength of 470 nm. DAT treatment also resulted in an improvement in device stability from 17 s (without treatment) to 99 s (with DAT treatment), and this was attributed to reduced ion migration due to a reduced concentration of Cl^- vacancies.

NPI Emitters. In addition to being grown as symmetrical, three-dimensional NCs, LHPs can also be synthesized as 2D nanoplatelets (NPLs). The common morphology of NPLs can be seen in Figure 126d. The thickness of these NPLs can be finely tuned from one monolayer (approximately 0.6 nm) to several monolayers. These perovskite NPLs exhibit quantum confinement when the thickness is smaller than the Bohr radius (typically 2–3 nm),⁴⁷ enabling a blue shift in the emission. This is currently simpler and more reproducible than growing perovskite NCs smaller than 3 nm.^{60,103} Perovskite NPLs have therefore gained significant attention for blue-emission applications, by allowing pure-bromide perovskites to emit at between 400 and 475 nm wavelength.⁶⁰ In 3D perovskite NCs larger than the Bohr radius, achieving these blue emission wavelengths requires using Cl-based or mixed chloride-bromide perovskites.¹⁰³ An important limitation is that Cl vacancies form deep traps that result in low PLQYs.^{103,1095} Although these limitations could be addressed through passivation, bromide-based perovskite NPLs are an important alternative. However, NPLs have a higher surface area to volume ratio, and exhibit pronounced surface defects. Originally, this limited the PLQYs to low values of 20% or less.^{47,209} However, Bohn *et al.* demonstrated that the PLQYs can be substantially increased up to 75% through surface passivation by adding $PbBr_2$ complexed with organic ligands to the colloidal solution.⁶⁰ Wu *et al.* also demonstrated that surface Br vacancies could be passivated using HBr, resulting in PLQYs up to 96% at a PL wavelength of ~460 nm,³⁹⁸ which is suitable for blue-emitters in ultrahigh definition displays.^{499,1111}

The use of passivation in bromide-based perovskite NPLs has led to improved performance with significantly improved color purity. An early report of perovskite NPL LEDs used $MAPbBr_3$ and $MAPbI_3$ NPLs complexed with long-chain butylammonium ligands. These NPLs were denoted $L_2[MAPbX_3]_{n-1}PbX_4$, where

X is the halide (either Br^- or I^-), L the butylammonium ligand,¹¹¹² and n the number of monolayers. It is noted that other groups would refer to these as simply $MAPbX_3$ NPLs.^{60,398} However, the Br-based perovskites contained a mixture of NPLs with different thicknesses, with electroluminescence from $n = 2, 3$, and 4 layers. The EQEs were all well below 0.01%.¹¹¹² Yang *et al.* subsequently developed a hot-injection approach to synthesize monodisperse $CsPbBr_3$ NPLs using the long-chain oleylamine, oleic acid, and octadecene as the ligands. By controlling the reaction temperature, they were able to fine-tune the number of monolayers in the NPLs, with fewer layers obtained at lower reaction temperatures. Using a reaction temperature of 180 °C, $CsPbBr_3$ NPLs with a thickness of 3.1 nm were obtained, which gave EL in LEDs at 480 nm. In both the PL and EL spectra, only one emission peak was obtained, and according to TEM analysis, there was a narrow distribution in the NPL thicknesses. The performance of the LEDs reached 0.1%, with a maximum luminance of 25 cd m⁻².²¹⁶ Through passivation of the $CsPbBr_3$ NPLs using HBr, Wu *et al.* achieved an improvement in EQE to 0.124%, with 62 cd m⁻² luminance. This was made possible using thinner NPLs with bluer emission at 463 nm. Color-pure emission was also achieved, with the fwhm of the EL peak being only 12 nm. As such, the CIE coordinates (0.157, 0.045) fulfilled the requirements for ultrahigh definition displays.³⁹⁸ However, the EQE falls well below the near-unity PLQY. Hoyer *et al.* investigated the limiting factors in $CsPbBr_3$ perovskite NPL LEDs. They found that when using PEDOT:PSS as the hole injector, there was significant nonradiative decay, leading to the PLQYs of the NPLs nearly halving. By adding a poly(triarylamine) layer between PEDOT:PSS and the NPL, nonradiative recombination was reduced, as found from time-resolved PL measurements. This led to an improvement in the EQEs by 2 orders of magnitude, from 0.007 to 0.3%, with 40 cd m⁻² luminance for blue emitters (464 nm EL wavelength).¹¹⁰² Similar results were obtained from sky-blue emitters (490 nm wavelength). Further improvements in EQE for the sky-blue emitters were achieved by adding $PbBr_2$ complexed with oleylamine and oleic acid for surface passivation, as previously detailed by Bohn, Tong, *et al.*⁶⁰ However, it was found that only a small amount (10 vol %) could be added to the NPL solution to improve the LED performance of the sky-blue emitters (from 0.24 to 0.55%).¹¹⁰² Further increases in the volume of the $PbBr_2$ -ligand passivating agent led to a reduction in performance. By contrast, Bohn *et al.* redispersed all of their purified perovskite NPLs into a solution of $PbBr_2$ -ligand in order to achieve the maximum improvement in PLQY.⁶⁰ It was also found that adding $PbBr_2$ -ligand to the blue-emitters led to no improvement in performance. While the reason behind the limitation in the amount of passivating agent that could be added is unknown, possibilities include the formation of an insulating shell around the NPLs that make charge-injection challenging.

Another approach used to passivate surface defects in $CsPbBr_3$ perovskite NPLs was to use soft Lewis bases. Zhang *et al.* used DDAB to partially replace the original oleylamine ligands through liquid-phase ligand exchange of the colloidal NPLs. The replacement of shorter DDAB ligand and the corresponding TEM images before and after the ligand treatment can be seen in Figure 126d. This increased the PLQY of blue-emitting perovskite NPLs from 45.1 to 69.4%, with a consequent increase in the device EQEs by an order of magnitude to 0.56%. Further improvements in EQE to 1.42%

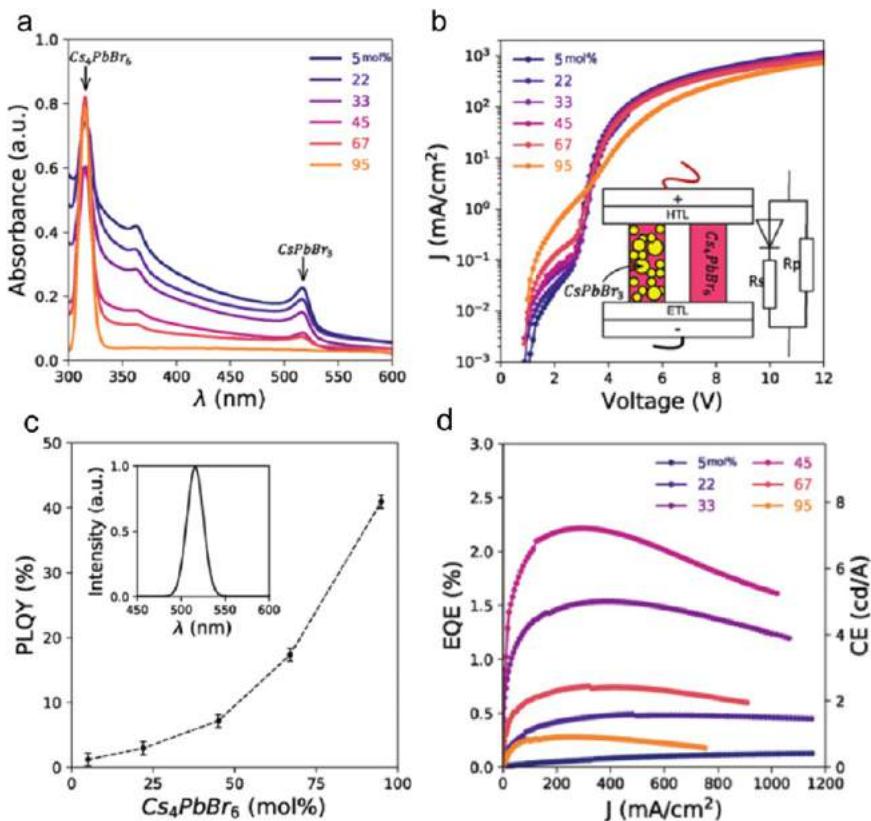


Figure 127. (a) Absorbance of $CsPbBr_3|Cs_4PbBr_6$ composite with different $CsBr$ and $PbBr_2$ precursor ratios. (b) Current density for devices based on the composite perovskites with different Cs_4PbBr_6 molar percentages. Inset: Schematic showing two types of current conducting channels ($CsPbBr_3$ -rich zone and Cs_4PbBr_6 -rich zone) through the perovskite layer in LED devices. The former channel could form a typical LED structure with a series resistor, whereas the latter one would serve as a shunt resistor due to the lack of emitter. (c) PLQY of composite films increased with an increased percentage of Cs_4PbBr_6 . Inset: Photoluminescence spectrum of composite films showing sharp peak near 516 nm with $fwhm = 20$ nm. (d) EQE for devices with respect to Cs_4PbBr_6 molar percentage. Reproduced with permission from ref 1114. Copyright 2018 John Wiley & Sons, Inc.

(shown in Figure 126i) were achieved by adding a layer of CBP between the poly-TPD hole injector and NPs. The role of the CBP was attributed to a reduction in the hole injection barrier, owing to the higher HOMO level of 6 eV. Furthermore, the stability of the LEDs also improved, with the time for the EL to reach half the peak value increasing from 15 to 42 s at a constant current of 1 mA cm^{-2} . Also, the PL stability was improved over time after ligand treatment, as shown in Figure 126e,h,g.¹¹⁰³ While short, these lifetimes are among the longest for blue perovskite NPs reported to date. Nevertheless, they are shorter than those achieved by sky-blue emitting perovskite thin films,¹¹¹³ and significant improvements in device operation stability are needed before the NP devices can be used commercially. It is believed that these effects are due to the DDAB ligands binding to surface bromide vacancies (XPS showed an increase in the Br/Pb ratio after adding DDAB), as well as to exposed lead cations on the surface.¹¹⁰³

An important challenge in the early development of perovskite NPI LEDs was poor knowledge of the exact band positions.¹⁰³ This was recently addressed through the use of Kelvin probe to measurements of the work function, and through X-ray photoemission spectroscopy to measure the valence band to Fermi level offset of blue and sky-blue emitting $CsPbBr_3$ NPs. According to these measurements, both emitters have deep ionization potentials of 6.8 eV (blue) and 6.5 eV (sky blue). As a result, conventional hole-injectors

would give rise to a large hole-injection barrier, whereas conventional electron-injecting materials would have a lower electron affinity or LUMO than the conduction band minimum of the NPs (3.8–3.9 eV). This was found to result in significant charge imbalance, which limits the EQEs of the devices, and indicates that future efforts need to focus on developing higher hole-injection level materials.¹¹⁰² Another alternative is to change the ligands to tune the band positions. Zhang *et al.* showed that partially substituting oleylamine for DDAB resulted in a reduction of the ionization potential of $CsPbBr_3$ NPs from 7.1 to 6.8 eV. Nevertheless, the hole-injection level remained deep.¹¹⁰³

Beyond $CsPbBr_3$, perovskite NPs using both Pb^{2+} and Sn^{2+} cations, and with halides ranging from I^- to Br^- to Cl^- have been grown, demonstrating PL emission wavelengths that can be tuned from 690 to 400 nm, although it should be noted that Cl -based NPs were not emissive.²⁰⁹ There is therefore potential to use perovskite nanoplates beyond solely blue emission (as it is in the cases that have been discussed previously), although there has been less focus on device development, since green, red, and near-infrared emitting thin films and NCs have already reached >20% EQE. Nevertheless, the ability of perovskite NPs to blue shift the emission of pure-halide materials may be advantageous in avoiding phase segregation and broadening of PL peaks that could be observed in mixed-halide perovskite thin films. However, further work is needed to improve the purity of iodide-based perovskite NPs,

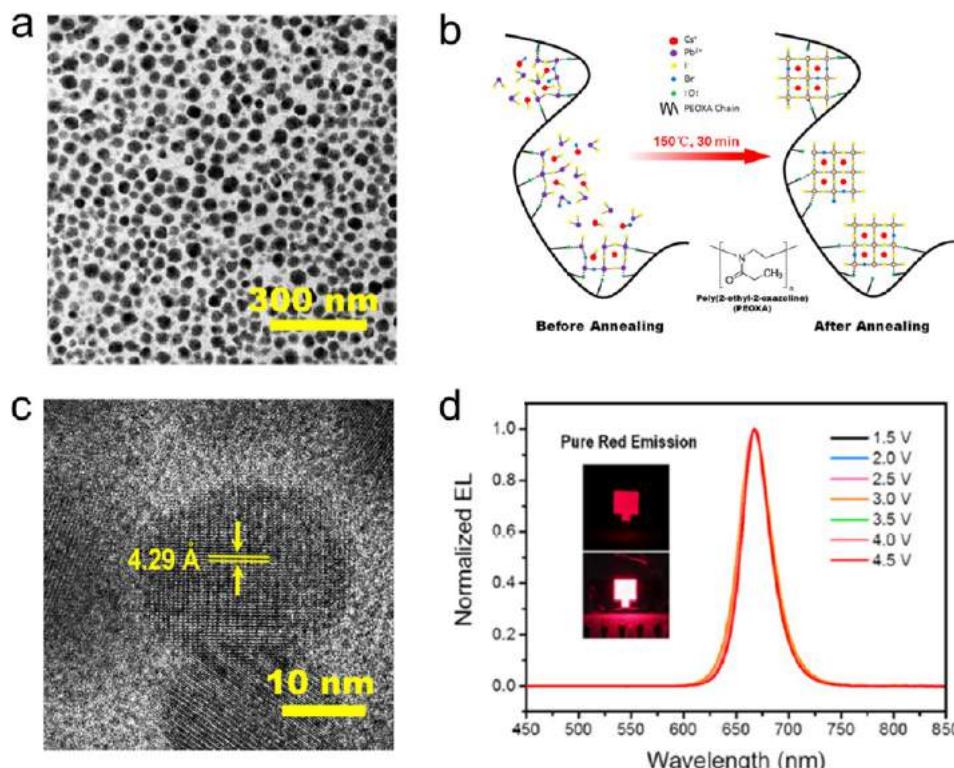


Figure 128. (a) TEM of $\text{CsPbBr}_{0.6}\text{I}_{2.4}$ film with 45% PEOXA. (b) Schematic diagram of polymer-induced *in situ* perovskite nanocrystal formation process. (c) High-resolution TEM image of crystals; the repeated distance of 4.29 Å indicates the (110) plane of $\text{CsPbBr}_{0.6}\text{I}_{2.4}$ lattice. (d) EL spectrum stability of the $\text{CsPbBr}_{0.6}\text{I}_{2.4}$ LED with 45% PEOXA. The inset is the photos of a light-up LED at voltage biases of 1.5 V (top) and 3.0 V (bottom). Reproduced from ref 1121. Copyright 2018 American Chemical Society.

with recent examples demonstrating broad PL fwhm values (50 nm at 650 nm wavelength) or multiple emission peaks.⁵⁴

NCs Embedded in 3D Matrices. 3D NCs embedded within a matrix of a lower dimensionality perovskite have been demonstrated, as discussed above. This enables charges to be more effectively confined in the 3D NCs, while having a well-controlled structure. An example that has gained attention recently is CsPbBr_3 embedded within a matrix of Cs_4PbBr_6 ,¹¹¹⁴ which is a wide-band-gap 0D non-perovskite. The absorbance due to Cs_4PbBr_6 is shown in Figure 127a. This composite structure has been shown to result in significantly improved PLQY. For example, Lian *et al.* found that CsPbBr_3 grown by thermal evaporation has a PLQY of 1.2%, whereas 5 mol % CsPbBr_3 embedded in Cs_4PbBr_6 has a PLQY of 40% (Figure 127c). This has been attributed to spatial confinement of charges, as well as the passivation of surface defects.¹¹¹⁴ In devices, this correlated with a significant improvement in device performance, from 0.13% for CsPbBr_3 LEDs to 2.5% for the composite devices with 55 mol % CsPbBr_3 (Figure 127d), a sketch of the device structure and device current density at different composite ratio are shown in Figure 127b).¹¹¹⁴ Similar improvements in performance were also observed by Shin *et al.*, from 0.0062% EQE for CsPbBr_3 to 0.36% for the composite, which was consistent with the improvement in the PLQY to 55% for the composite. Optical modeling found the outcoupling of these devices to be similar, between 9 and 12%, and the calculated internal quantum efficiencies were 0.072 and 2.9%, respectively. From this, it was calculated that the injection efficiency was lower for the composite, in agreement with the wide band gap of the Cs_4PbBr_6 host.¹¹¹⁵ Both Lian *et al.* and Shin *et al.* grew the composite films through the

evaporation of CsBr and PbBr_2 in alternate layers and adjusting the ratio of the thicknesses of each layer. However, Shin *et al.* reported that a limitation with this technique is that CsPbBr_3 formed in the Cs_4PbBr_6 is not stable and is affected by exposure to moisture. Indeed, they reported that the as-grown film (that was nominally Cs_4PbBr_6) was originally yellow-colored CsPbBr_3 that became transparent Cs_4PbBr_6 with embedded CsPbBr_3 after 15 min in ambient air. After several days in air, the film had completely become Cs_4PbBr_6 and no green emission was observed.¹¹¹⁵ This therefore shows the limitation of $\text{Cs}_4\text{PbBr}_6/\text{CsPbBr}_3$ composites prepared by the sequential deposition approach, even though Lian *et al.* reported that the composite was more stable under operation than CsPbBr_3 .¹¹¹⁴

Composites comprising PbS quantum dots heteroepitaxially incorporated in perovskite matrices have also been demonstrated with success.¹¹¹⁶ These structures are particularly advantageous for devices emitting in the near-infrared at wavelengths (900–1560 nm) longer than achievable with pure lead perovskite emitters.¹¹¹⁷ Such long wavelength emitters are important for applications in night vision, biomedical imaging, optical communications and computing,¹¹¹⁸ and the ability to achieve these devices using low-cost solution-based methods could be significantly advantageous over the epitaxial structures currently used.¹¹¹⁷ PbS can form heteroepitaxially in MAPbI_3 lattices because they have strong structural affinity and similar Pb–Pb bond distances (5.97 Å for PbS, 6.26 Å for MAPbI_3) that are within 4.6% of each other.¹¹¹⁶ Further improvements in lattice matching could be achieved by alloying I with Br in the perovskite due to reductions in the lattice parameter of the perovskite.¹¹¹⁸ Theoretical considerations also showed that it is

possible for PbS/MAPbI₃ interfaces to form without defects. HRTEM measurements showed a well-defined orientation between PbS and MAPbI₃. The growth of the MAPbI₃ matrix around the PbS quantum dots was achieved by exchanging the organic ligands for short halide ligands. By mixing with PbI₂ dissolved in butylamine, the PbI₂ formed a complex with the halide species on the quantum dot surface. This complex was deposited onto a surface by spin-coating, followed by soaking in a solution of methylammonium iodide in isopropyl alcohol, thus forming the MAPbI₃ matrix. Changing the ratio of PbI₂ and quantum dot in the precursor changed the final content of the quantum dots in the matrix from 0.2 to 29%.¹¹¹⁶ Spectroscopic measurements showed that the efficiency of carrier transfer to the PbS was up to 80%.¹¹¹⁶ Demonstrations of near-infrared LEDs achieved EQEs up to 5.2% at 1390 nm emission wavelength, which was significantly higher than the PbS quantum dot only control (0.03%).¹¹¹⁸ Further improvements in performance were achieved by embedding PbS quantum dots in a 2D perovskite matrix, with phenethylamine used as the stabilizing agent bound to the PbS quantum dots. This was mixed into the solution containing the inorganic precursors (CsBr, PbBr₂), which was spin-coated, with toluene dripped as the antisolvent. GISAXS measurements showed that this resulted in quantum dots that were regularly and evenly spaced (on average 4.4 nm apart). Spectroscopic measurements showed that the exciton transfer efficiency from perovskite to quantum dot was 82% at 1533 nm emission wavelength, with LEDs achieving 3.5% EQE. For 1300 nm emission wavelength, the EQE was 6%, but the highest EQE was achieved for 986 nm emission, with a peak value of 8.08%. The increases in EQE with shorter wavelength were due to increased PLQY in the quantum dots.¹¹¹⁷ These devices also demonstrated improved stability compared to earlier quantum dot in perovskite versions, with the EL intensity reaching half the peak value after 1 h of operation.¹¹¹⁷

NC–Polymer Composites. Perovskite NC–polymer composites have been explored as a means to improve the stability of the NCs.^{20,469,1119,1352} Xin *et al.* demonstrated blends of CsPbBr₃ NCs with the PMMA, PS, and poly(butyl methacrylate). These composites were able to maintain their quantum yield in air for more than a month.¹³⁵² Wang *et al.*²⁸⁵ also reported a swelling–deswelling microencapsulation strategy to fabricate MAPbBr₃ NC/polymer composite films which were stable against moisture and heat. Perovskite–polymer composites have also been shown to result in reduced nonradiative recombination and improved device performance. Zhao *et al.* demonstrated this with perovskite thin films. They embedded a 2D/3D bulk perovskite into an insulating polymer matrix, resulting in near-infrared LEDs with EQEs reaching 20.1%.¹⁰⁷⁹ The polymer component suppressed nonradiative recombination at the interfaces between the perovskite emissive layer and charge transport layers. Li *et al.* demonstrated improved performance in perovskite LEDs using perovskite NC/polymer composites. They fabricated a composite of MAPbBr₃ NCs and an aromatic polyimide precursor (PIP). By adding the PIP polymer matrix, the EQE was increased by 2 orders of magnitude compared with pristine MAPbBr₃ NCs in a thin film, giving an EQE of 1.2%.¹¹²⁰ Cai *et al.* blended CsPb(Br,I)₃ NCs in different ratios with the polymer poly(2-ethyl-2-oxazoline). The TEM images are shown in Figure 128a,c. This resulted in improved EQEs in pure-red LEDs from 1.04% (0 wt % polymer) to 6.55% (45 wt % polymer).¹¹²¹ The enhancement of EQE and stability are

attributed to strong interactions between the functional group in the polymer matrix and the Pb²⁺ in NCs, which facilitates homogeneous distribution of NCs and increases the PLQY (Figure 128b). The EL spectra is stable under different operational voltage as shown in Figure 128d. In addition to homogenous distribution of NCs, Rainò *et al.* suggested the improvement of spectra stability is due to that the high hydrophobicity and efficient molecular packing of the polymer matrix with the long-chain NC surface ligands are the key factors for protecting the NCs against environmental damage.¹¹²² The polymer matrix also provides excess nucleation sites during the NC recrystallization process, which leads to more uniform NC distributions in the films, resulting in a higher PLQY in thin films of the composite.¹¹²¹ Another promising application of the perovskite NC/polymer composites is as down-converters. Through excitation with commercial blue LEDs, these down-converters efficiently produce sharp green and red photoluminescence, which is important for display applications.^{278,1123} Start-up companies are beginning to explore the commercial potential of perovskite NC/polymer composite phosphors.¹¹⁰⁰ However, devices are still limited by the thermal stability of the composite materials. For example, LEDs using MAPbBr₃ NCs/Polyvinylidene fluoride composites undergo thermally induced degradation when temperature exceeds 70 °C.²⁷⁸

Optical Features of Perovskite Light Emitters. Highly Efficient Light Emission. The emergence of LHP NC systems as a novel class of light-emitting materials may offer additional technological possibilities, as reflected by the enormous enhancement of photoluminescence quantum yield in the past 5 years. The defect-mediated nonradiative losses in the bulk LHPs are often considerable, but in the NC systems, strategies including composition engineering, ligand passivation, quantum and dielectric confinement, and post-treatments of LHP thin films and NCs, have shown promise. For example, Hassan *et al.* achieved a η_{PL} of >93% in cubic MAPbI₃ NCs synthesized by the LARP technique.¹¹²⁴ In the mixed-cation NCs, *e.g.*, FA_{0.5}MA_{0.5}PbBr₃, near-unity η_{PL} was also achieved.¹¹²⁵ Pan *et al.* synthesized highly luminescent red CsPbI₃ NCs with η_{PL} of >95% using bidentate 2,2'-iminodibenzoic acid as ligands to passivate NC surfaces.¹⁷² Near-unity η_{PL} was also reported in CsPbI₃ NCs,¹¹²⁶ as well as other CsPbX₃,⁷⁸ by stabilizing the cubic phase using trioctylphosphine lead iodide precursor and passivating the surface with alkylammonium ligands using the hot-injection methods. Additional strategies, such as selective chemical etching¹¹²⁷ and spray pyrolysis synthesis,¹¹²⁸ were also reported to significantly enhance η_{PL} to near-unity.

In quantum-confined LHP NC systems, η_{PL} enhancement generally requires more efforts. For example, the quasi-2D PEA₂A_{1.5}Pb_{2.5}Br_{8.5} NCs, where A = MA and Cs, exhibit a high η_{PL} of 88%.¹⁰⁸² In the 2D (RNH₃)₂[MAPbBr₃]₃PbBr₄ NPL system, where R is an alkyl chain, and η_{PL} in the assembled superlattices can reach 90%,¹¹²⁹ hypothetically due to a special aggregation-induced emission mechanism. An important merit for 2D material-based emitters is that the exciton transition dipole moments (TDMs) can be aligned parallel to the surface plane, guiding the emission perpendicular to the out-of-plane direction, which greatly enhances the light outcoupling efficiency in LEDs.^{1125,1130} Recent advances in 2D CsPbBr₃ and MAPbBr₃ NCs have shown that one can obtain a high degree of in-plane TDM ratio in their superlattices, showing promise for future photonic devices.^{751,1131}

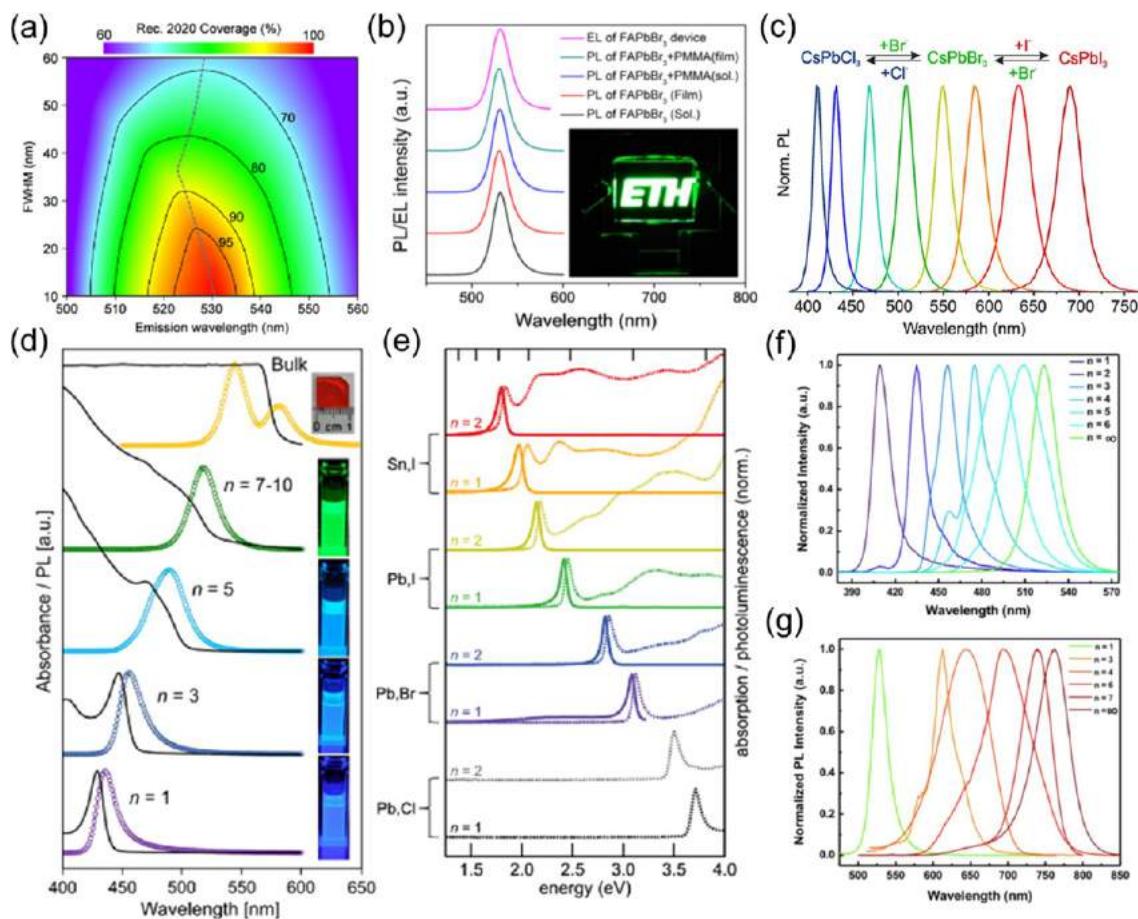


Figure 129. Fundamental characteristics of lead-halide perovskites. (a) Calculated Rec. 2020 color gamut coverage in CIE 1931 color space as a function of fwhm and emission wavelength for the green emitter. (b) PL and EL spectra of FAPbBr₃ NCs that achieved Rec. 2020 gamut area coverage >97%. Reprinted from ref 900. Copyright 2017 American Chemical Society. (c) Tunable PL spectra in the colloidal CsPbX₃, where X = Cl, Br, and I, NCs using fast anion exchange either from bromide to iodide (red shift) or bromide to chloride (blue shift). Reprinted from ref 55. Copyright 2015 American Chemical Society. (d) Absorption and tunable PL spectra of 3D bulk single-crystal and colloidal solution of 2D MAPbBr₃ NCs with precise layer control between $n = 7$ – 10 and $n = 1$. Reprinted from ref 211. Copyright 2016 American Chemical Society. (e) Absorbance and highly tunable PL spectra of 2D LHPs by varying the B-site cations, Pb and Sn, and anions, Cl, Br, and I. Reprinted from ref 209. Copyright 2016 American Chemical Society. (f,g) Tunable PL spectra in the layered quasi-2D perovskite (Br-based (f) and I-based (g)) NCs. Reprinted with permission under a Creative Commons CC BY license from ref 1138. Copyright 2018 The Authors.

Narrow Emission Band. Bright and narrow-band fluorophores as primary colors emitting at pure red (R), green (G), and blue (B) wavelength regions are critical to enable next-generation displays with extremely high chromaticity. The emergence of LHP NC-based LEDs is mainly driven by their intrinsically narrow-band emission, whose fwhm ranges from 9 to 42 nm, from B to R.^{23,105,411} Notably, an extremely narrow fwhm of 11 nm had been reported in the layer-controlled 2D CsPbBr₃ NC solutions.⁶⁰ In LEDs, the fwhm of 14.7 nm has been realized using the mixed anion CsPbBr₃/Cl₃ NCs with appropriate ligand engineering.¹¹³² Sim *et al.* reported bright EL based on CsPbX₃, giving narrow fwhm values of 16, 16, and 40 nm for B, G, and R primaries, respectively.¹¹³³ A report demonstrated that the PL fwhm decreased from 36 to 32 nm when the CsPbI₃ NCs were encapsulated by varying the amount of ammonium thiocyanate.¹¹³⁴ Zhang and co-workers achieved a very narrow EL fwhm of 33 nm for the R primary at 648 nm using the CsPb(Br/I)₃ NCs.¹⁰⁹⁸ By cross-linking the CsPbI₃ perovskite NCs with trimethylaluminum, the fwhm further reduced to 31 nm for the R primary.¹⁰⁶⁷ In the NIR wavelength region, by modulating the anion and cation

compositions, the EL fwhm was reported to as low as 27 nm in the Cs_xFA_{1-x}Pb(Br_{1-y}I_y)₃ NCs, optimized by an automated microfluidic platform.¹¹³⁵

Although narrow electroluminescence peaks can be realized in the green-emitting CsPbBr₃ NCs, the resulting color gamut area would only cover 90% of the recommendation (Rec.) 2020 standard, the newly defined color gamut for next-generation displays, because the emission peaks are at <520 nm wavelength.⁵² Using the colloidal 2D FAPbBr₃ NCs with a fwhm of 22.8 nm peaking at 529 nm, a coverage of >98% Rec. 2020 has been reported (Figure 129a,b).^{900,1136,1137} We consider that the perovskite NC emitters would be the most promising candidate reaching 100% of the Rec. 2020 color gamut among all semiconductor systems.

Tunable Emissive Spectra. The emission spectra and corresponding optical band gaps in the LHPs are continuously tunable over the entire visible spectral region from 400 to 780 nm. A few strategies, including stoichiometric mixing and quantum confinement were utilized to tune the optical band gap of the perovskite NCs, as amply discussed in previous sections. For example, Nedelcu *et al.* demonstrated emission

wavelength tunability in the CsPbX_3 NCs by fast anion exchange at 40 °C (Figure 129c).⁵⁵ The NCs exhibit η_{PL} of 10–80% and fwhm of 12–40 nm. A similar approach was reported by the Akkermann *et al.* by exchanging bromide anions using iodide and chloride precursors.⁵⁷ Similar approaches were also carried out in the MAPbX_3 and FAPbX_3 systems.^{29,163} For the RP-phase quasi-2D NPs the PL emission can also be tuned between 410 and 523 nm for $(\text{BA})_2(\text{MA})_{n-1}\text{Pb}_n\text{Br}_{3n+1}$ (Br series) (Figure 129f), and between 527 and 761 nm for $(\text{BA})_2(\text{MA})_{n-1}\text{Pb}_n\text{I}_{3n+1}$ (I series) (Figure 129g).¹¹³⁸ Note that although the anion exchange enables viable band gap tunability, the high η_{PL} of the mother NCs is not always preserved.⁵⁵ Moreover, the solubility of chloride precursors in the common polar solvents is generally low, making it more difficult to prepare blue emitters.⁸⁹⁹ The emission spectra can also be modulated by temperature (temperature-dependent PL studies have mainly been used to investigate the excitonic properties of LHPs).

One-dimensional quantum confinement by controlling the lattice layer number in 2D NPs is another attractive approach to enable emission blue shift.^{16,18,48,743,895,1124} Note that the 2D NPs are different from the RPPs, which are quasi-2D phases comprising stacked 2D layers. Considerable efforts have been made in the 2D MAPbX_3 , CsPbX_3 systems using the LARP, nonsolvent crystallization, and hot-injection technique.^{209,1139} For example, the Tisdale group identified the colloidal 2D MAPbBr_3 perovskites with layer numbers (n) of 4, 5, and 6 emitting at 475, 490, and 504 nm, respectively.¹⁹ By gradually varying the octylammonium ligand concentration between 100 and 0%, the colloidal 2D MAPbBr_3 NCs were isolated giving emission between 427 and 519 nm for $n = 1$ to ∞ .¹⁶ The Tisdale group also demonstrated thin layers of $n = 1$ and 2 using the nonsolvent crystallization method (Figure 129e).²⁰⁹ The Shih group reported high η_{PL} of up to 90% in the 2D NC solutions of $n = 1, 3, 5$, and 7, yielding stable room-temperature EL at 436, 456, 489, and 517 nm, respectively (Figure 129d).⁸⁹⁹

Electrical Features of Nanocrystal Perovskite Light Emitters. Charge Carrier Dynamics. While there has been tremendous progress in the performance of perovskite NC LEDs, future improvements will require a more in-depth understanding of the intrinsic photophysics of these materials, and also how charge carriers are transported across interfaces within the devices. The recombination rate of free carriers can be described by eq 3:^{1140–1142}

$$\frac{dn(t)}{dt} = -k_1 n - k_2 n^2 - k_3 n^3 \quad (3)$$

where t is time, n is charge carrier density, k_1 is recombination rate of exciton recombination or trap-related recombination, k_2 is the bimolecular recombination rate of free charge carriers, and k_3 is the Auger (multi charge carrier) recombination rate. By comparing the charge carrier dynamics of polycrystalline perovskite bulk thin films and perovskite NC films using steady-state and transient photoluminescence spectroscopy, Kim *et al.*¹¹⁴² and other researchers found out that both exciton recombination and bimolecular recombination occur in bulk thin films, while exciton recombination is dominant in NC thin films.^{29,1062,1142,1143} Further details on the physics of hot carrier relaxation and exciton recombination are given in **Charge Carrier Dynamics** section.

As the main radiative recombination of perovskite NCs is due to exciton recombination, it is important to understand the

source of band-edge exciton generation inside NCs. During photoexcitation, photons with energy higher than the band gap will create hot carriers. The interactions between carriers (carrier–carrier interactions) and the surrounding lattice (carrier–phonon interactions) play an important role in hot carrier cooling processes in perovskite NCs which generate band-edge excitons or cold carriers.^{50,1144} The radiative recombination of these single band-edge excitons is the main contribution of photon generation in a perovskite NC light-emitting diode. Another pathway to create band-edge excitons is through biexciton or multiexciton generation processes. When the incident photon energy is higher than $2hn$ during the photoexcitation process, the excess energy of the generated hot carriers can create additional excitons.³¹² Then, the bi/multiexcitons will recombine nonradiatively through an Auger process and form band-edge excitons.^{872,1145} The hot carrier cooling rate can be influenced by several factors including excitation energy,⁸⁷² halide compositions⁸⁵² and types of cations.¹¹⁴⁶ The reader can consult the **OPTICAL PROPERTIES** section for more details on this topic.

Carrier trapping will also influence the carrier dynamics in perovskite NCs for light-emitting applications. It occurs when the band-edge excitons do not recombine radiatively and instead migrate to a trap state which is close to the band-edge.^{21,872} As perovskite NCs still suffer from a broadening in the photoluminescence peak, it is important to understand what gives rise to this effect.^{1147,1148} Wehrenfennig *et al.*¹¹⁴⁸ suggested that the homogeneous PL broadening could be increased through phonon creation and annihilation which would generate side peaks, or through polaronic effects where the photogenerated electron–hole pair is strongly coupled to the surrounding lattice, causing a geometric lattice relaxation and a Stokes-shifted emission from the absorption edge. A typical Stokes shift for CsPbBr_3 NCs with effective edge length between 4 and 13 nm ranges from 20 to 80 meV.⁷⁸⁵ Brennan *et al.* reported that the size-dependent Stokes shift is intrinsic to the NC electronic structure and independent from extrinsic influences such as solvents and impurities.⁷⁸⁵ Another factor which can influence the band structure and hence the Stokes shift is temperature. Naghadeh *et al.*¹¹⁴⁹ reported that the PL spectra will exhibit a blue shift for small NCs (~ 3.1 nm) with decreasing temperature from 300 to 20 K, while exhibiting a red shift with decreasing temperature for medium-sized (5.1 nm) and large (9.2 nm) NCs. The size of NC will also influence the carrier dynamics as the PL lifetime increases with temperature for larger NCs, and it remains the same for the small and medium-sized NCs.

The majority of investigations into perovskite NC carrier dynamics are performed on solutions or thin films under photoexcitation. Future insights into the carrier dynamics of the NCs under electrical excitation are also needed. Sharma *et al.*⁹⁹⁰ recently demonstrated that the NCs aggregates in the thin film did not blink in PL but showed strong blinking in EL. This is because that all NCs can be photoexcited spontaneously and emit photons during the photoluminescence process. However, only a small fraction of the NCs within the aggregates can undergo electroluminescence, the majorities remain dark permanently, resulting in blinking. By investigating CsPbBr_3 NCs system ($\sim 16 \pm 5$ nm), they reported that the selective EL process is due to charge migration and selective recombination. During the electroluminescence process, the injected charges will migrate to larger NCs that have smaller band gaps. As a result, the larger

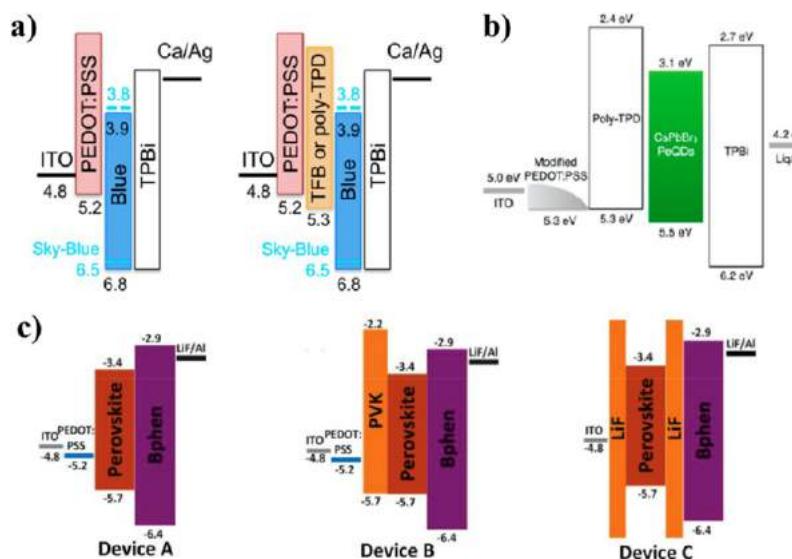


Figure 130. Band structure illustration of perovskite LEDs with different interfacial layers. (a) Blue and sky-blue emitting perovskite NPL LEDs with or without an interfacial layer of TFB or poly-TPD. Reprinted under a Creative Commons CC-BY license from ref 1102. Copyright 2019 American Chemical Society. (b) HTL modification: energy diagram for modified hole injection layer (Nafion blending PEDOT:PSS). Reproduced from ref 190. Copyright 2017 American Chemical Society. (c) Comparison of devices with different interfacial layers. Device A: PEDOT:PSS/perovskite/Bphen. Device B: PEDOT:PSS/PVK/perovskite/Bphen. Device C: LiF/perovskite/LiF/Bphen. Reprinted with permission ref 1163. Copyright 2018 John Wiley & Sons, Inc.

NCs function as traps where the charges migrating over other NCs get accumulated and recombined. It shows that under comparable excitation rates, the intrinsic ELQY is only 36% that of the PLQY.⁹⁹⁰ During photoluminescence, simultaneous emissions can occur on all NCs after photoexcitation and exciton recombination. However, when injecting carriers, only a larger NC will emit as it acts as a trap center due to its lower band gap energy.

Role of Contact Layers and Charge Balance. Charge balance and the charge injection barrier are two parameters that are strongly linked together because they are determined by the position of the perovskite bands relative to the band positions of the materials for injecting electrons and holes. The most common organic and inorganic charge injection materials are detailed in several reviews, *e.g.*, reference.^{801,1150–1152} From these, is evident that the most common charge injectors enable efficient electron injection over the full range of perovskite electron affinities (down to 3.1 eV for MAPbCl_3),^{1150,1153} but hole-injection is more challenging. While the hole-injection level for typical materials is up to 5.4 eV (for TFB and poly-TPD),¹¹⁵⁰ the perovskite ionization potential can reach values as high as 6.8 eV for blue-emitting CsPbBr_3 perovskite NPLs.¹¹⁰² Green-emitting perovskites also have higher ionization potentials (*e.g.*, 5.9 eV for MAPbBr_3).¹¹⁵⁰ Higher hole-injection levels have been achieved through modifications in common organic materials. For example, PEDOT:PSS has been mixed with MoO_x to increase the work function from 5.20 to 5.62 eV.^{1115,1154} As another example, Nafion perfluorinated ionomer (PFI) has been used to modify the surface of TFB. The surface dipole from PFI gives rise to band bending of the TFB beneath to a higher work function, resulting in an improvement in the performance of blue-emitting $\text{CsPbBr}_{3-x}\text{Cl}_x$ NCs.¹¹⁵⁵ Similarly, Chiba *et al.* also reported using Nafion blending with PEDOT:PSS to modify the workfunction of PEDOT:PSS, as shown in Figure 130b.¹⁹⁰

Charge balance is measured by constructing two single-carrier devices from the same perovskite emitter. One device

has hole-injecting and hole-selective contacts on both sides (*e.g.*, ITO/PEDOT:PSS/perovskite/ MoO_x /Au). The other has electron-injecting and electron-selective contact which have deep ionization potentials or HOMO levels to block holes (*e.g.*, ITO/ZnO/PEI/perovskite/TPBi/Ca/Ag). By controlling the polarity of the applied bias, hole or electron injection from each of the injecting layers is measured, and the current densities for electrons and holes are compared. Unbalanced current densities would result in the recombination zone being close to the electrode with the less efficient injection. For example, a higher electron current density would imply that the recombination of injected electrons and holes occur at hole-injector interface. In such cases, it is important to ensure that the electron affinity or LUMO of the hole-injector is sufficiently low to confine carriers within the active layers in order to avoid parasitic emission from the injecting layer.

The size of the injection barriers may be inferred from the built-in potential of the device, which is measured through electroabsorption spectroscopy,¹¹⁵⁶ or is determined through photoemission spectroscopy measurements of the individual layers. Details and best practices of the latter approach are given in reference.⁸⁷⁰ It should be emphasized that owing to strong spin–orbit coupling, perovskites often have significant tailing in the density of states at the valence band maximum, and accurately determining the valence band to Fermi level offset would require fitting the density of states to the valence spectrum rather than through simple linear fits.^{1102,1157} Another approach to measure the work function is to perform Kelvin probe measurements, which has the advantage of measuring the work function of the layers under ambient conditions that may be more representative of the films in devices. Details on best practices on Kelvin probe measurements on perovskites are given in reference.¹¹⁵⁸

Careful choice of the charge-injection layers is necessary not only to minimize injection barriers and control charge-balance, but also to minimize nonradiative recombination at the interfaces. PEDOT:PSS is one of the most common hole-

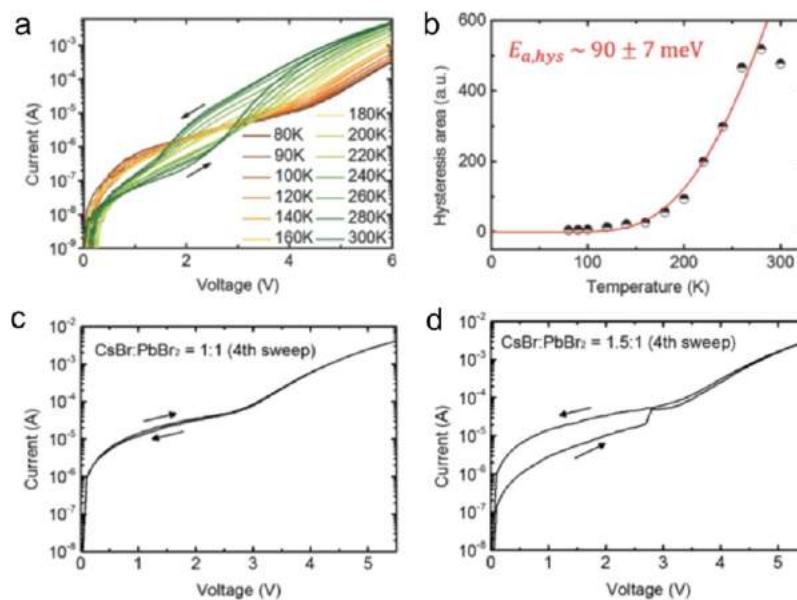


Figure 131. (a) Temperature-dependent current–voltage characteristics of the CsPbBr_3 PeLED showing current hysteresis. (b) Plot of hysteresis area *versus* T with a nonlinear fitting based on Arrhenius equation. (c) Hysteresis behavior of a CsPbBr_3 PeLED with $\text{CsBr}:\text{PbBr}_2 = 1:1$ (based on Buf-HIL) at room temperature with four sweeps. (d) Hysteresis behavior of a CsPbBr_3 PeLED with $\text{CsBr}/\text{PbBr}_2 = 1:5$ (based on Buf-HIL) at room temperature with four sweeps. Reproduced with permission from ref 1168. Copyright 2017 John Wiley & Sons, Inc.

injection materials deposited beneath the perovskite active layer but has in many cases been shown to give high rates of nonradiative recombination with both bulk 3D perovskites and perovskite NPs,^{1102,1159} leading to lower external PLQYs and fast PL decay. This is due to the semimetallic nature of PEDOT:PSS and high density of defect states that would occur at the interface.¹¹⁵⁹ The effects of nonradiative recombination at the interface with PEDOT:PSS has been addressed through the use of poly(triarylamine) interlayers between PEDOT:PSS and perovskite. For example, the use of TFB or poly-TPD resulted in an increase in the PL decay time of blue-emitting CsPbBr_3 perovskite NPL thin films deposited on top, which led to the device EQE improving by 2 orders of magnitude, as shown in Figure 130a.¹¹⁰² Similarly, it has been found that adding a 20 nm layer of poly-TPD between PEDOT:PSS and MAPbI_3 in solar cells resulted in a significant reduction in leakage current, along with an increase in the open-circuit voltage.¹¹⁵⁹

Work on reducing interface recombination has also focused on passivating the perovskite, though this has to date largely been demonstrated in photovoltaic systems. This includes the use of surface passivating species such as alkali metal-halide additives and generation of 2D/3D surfaces that significantly reduce nonradiative recombination at the interfaces.^{1160–1162} Another important consideration for the device performance is the charge leakage, which refers to the escape of holes and electrons from the perovskite layer to the charge transport layer. To solve the leakage issue, Shi *et al.* proposed an LiF double insulating structure shown in Figure 130c.¹¹⁶³ The sandwiched FAPbBr_3 perovskites are protected by LiF layers to avoid leakage, which increases the EQE to 5.53% device C, compared to that of devices A and B, which is 0.174%.

Ion Conductance and Hysteresis. Typically, perovskite LEDs are only measured in one voltage direction. In many cases, this is due to the device degrading toward the higher voltage end of the measurement. However, measurements of

the forward and reverse sweep of nondegraded perovskite LEDs have shown hysteresis to be present,³¹ similar to observations made in perovskite solar cells. In photovoltaics, hysteresis is attributed to ion migration, owing to the high density of halide ions and vacancies present in the perovskite material.

Changing the distribution of ions at the interface impacts charge collection (in a solar cell) or injection (in an LED); in certain configurations, this may be more favorable, but typically, this creates unwanted barriers to charge movement at the interfaces.¹¹⁶⁴ Furthermore, these interfacial halides and vacancies may also lead to nonradiative recombination sites as the very ions or defects may introduce trap states in the band gap, particularly at surfaces.¹¹⁶⁵ We note that such ion migration effects can also be seen as an opportunity, as demonstrated by light-emitting electrochemical cells,^{1166,1167} in which the devices are designed such that the local distribution of ions allows for favorable injection and emission properties. However, achieving control over the ionic movement will be critical for its practical use.

Work by Cho *et al.*¹¹⁶⁸ on CsPbBr_3 thin film LEDs showed that the degree of current hysteresis increased exponentially with temperature, following an Arrhenius relationship that had an activation energy of 90 ± 7 meV. This is close to the reported activation energy for halide anion migration in MAPbBr_3 and it was proposed that the migration of Br^- accounts for the current hysteresis observed at different temperatures (Figure 131a,b). When the ratio of $\text{CsBr}/\text{PbBr}_2$ was increased from 1:1 to 1.5:1 in the precursor solution, the current hysteresis from the resultant films became worse (Figure 131c,d), possibly due to an increase in trap density. With higher $\text{CsBr}/\text{PbBr}_2$ ratio, the hysteresis increased up to fourth sweep compared with low $\text{CsBr}/\text{PbBr}_2$ ratio.¹¹⁶⁸ Chen *et al.* also found that ions migrated with the application of an electric field of 0.3 V m^{-1} vertically in a MAPbBr_3 microplatelet, enabling the formation of a p–i–n junction,

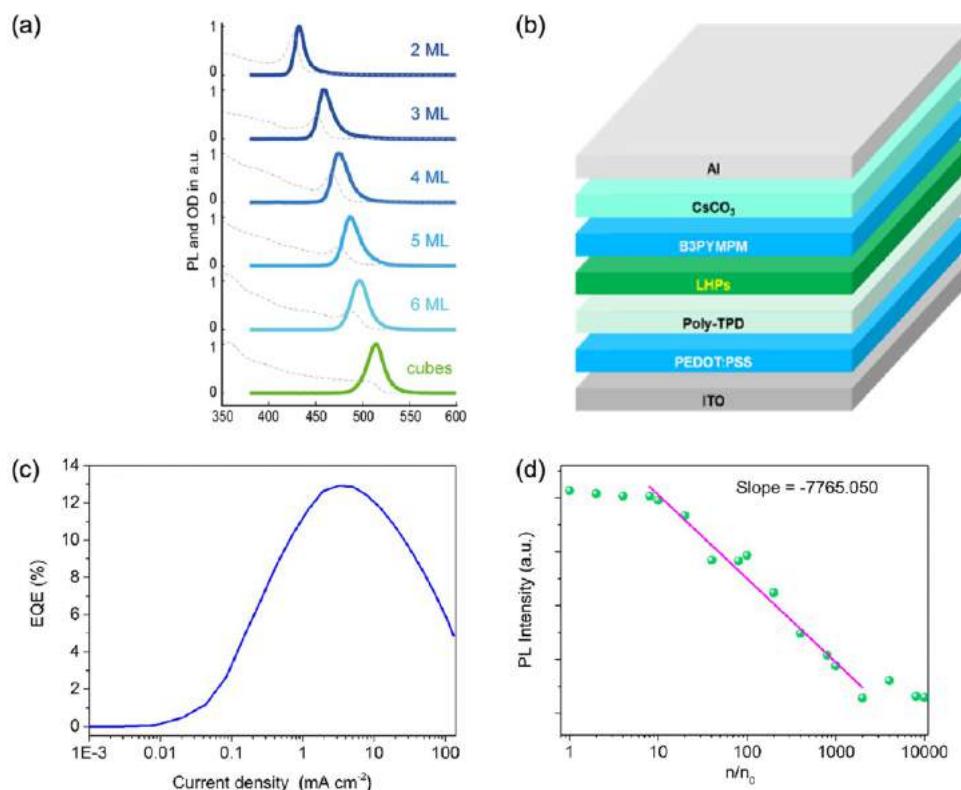


Figure 132. (a) PL (solid) and absorption (dashed) spectra of CsPbBr₃ colloidal nanoplatelet with different thicknesses. (b) Scheme structure of LHP-LED. (c) EQE current density characteristics of LHP-LEDs. (d) PL intensity dependence of MAPbBr₃ film on electron number, and n_0 is the density of electron injected when the current density is 1.0×10^{-2} mA cm⁻². Panel a is reprinted with permission under a Creative Commons CC-BY license from ref 60. Copyright 2018 The Authors. Panel d is reprinted from ref 1187. Copyright 2018 American Chemical Society.

which could be frozen in place by rapidly cooling to -193 °C. This operated as an LED, with negligible current hysteresis at -193 °C, but significant hysteresis at ambient temperature, which is again consistent with ion migration giving rise to the observed hysteresis.¹¹⁶⁹ Such ion migrations results in halide segregation in LHP NCs with mixed-halide composition. Under photoirradiation or with an applied bias, mixed-halide perovskites present a main limitation due to the segregation of the mixed phase into two phases, as initially reported by Hoke *et al.*¹¹⁷⁰ For example, in the ensemble film of CsPbBr_{1.2}I_{1.8} NCs, Zhang *et al.*¹¹⁷¹ observed that the laser excitation causes a blue shift from 630 to 520 nm in the PL peak that can revert back in the dark. Interestingly, for an isolated single CsPbBr_{1.2}I_{1.8} NC, the PL is also blue-shifted upon laser excitation but never returns back in the dark, revealing the fact that the presence of adjacent NCs is crucial to channel the migration of iodide ions. Furthermore, they observed blue-shifted PL when the NCs were electrically biased in the dark without the injection of excited-state charge carriers. This finding suggests that the local electric field breaks the iodide bonds that triggers the ion migration process.¹¹⁷¹ Gualdrón-Reyes *et al.* found that such segregation is a size-dependent phenomena and is minimized in thin films of smaller size NCs.¹¹⁷² Similarly, the spectral instability of the PeLEDs is observed under varying bias when mixed Cl/Br halide is used for blue EL. Wang *et al.* reported EL red shift as a function of Cl content caused by strong electrical field.¹¹⁷³ It was found that the deeper blue device appeared to be more subjected to the field-induced phase separation.

LEDs Exploiting Lead-Halide Perovskite Emitters. By virtue of superior features in light generations and electrical characteristics, lead-halide perovskites, especially the NCs, were supposed to be contemporary soft light emitters in flexible thin film light-emitting diodes.^{396,404,499,1085} In addition to the cost advantage endowed by cheap raw materials, facile synthesis of emitters and solution processing film deposition, LHP-LEDs also demonstrate high luminous efficiency, high-color purity, and ultrawide color gamut for prospective full-color display, white lighting, and other applications.^{169,175,404,499,1083,1084,1128} Thus, far, some impressive achievements have been reported in the few years, including a high external quantum efficiency level over 20%, ultrahigh brightness level over 100 000 cd m⁻², a good flexibility, a facile device fabrication, but an incongruous operation stability.^{396,404,1078,1117,1143,1147} Because of the environment-friendly consideration of lead component, some lead-free metal-halide perovskite emitters were also developed and great progresses, *e.g.*, high-color rendering index over 90, were achieved.⁴⁹⁹ However, limited by a high-quality film deposition, these emitters are more compatible with inorganic LEDs as phosphors.^{499,1105} This section mainly concentrates onto the LEDs exploiting LHP emitters.

Classifications. Like other solution-processed thin film devices, such as QD-LEDs and polymer solar cells, the device structures of most LHP-LEDs are simple, and their primary difference are the emitters. Thus, the classification of LHP-LEDs is mainly based on the colors, dimensions, film deposition technologies, and other features of LHP emitters.

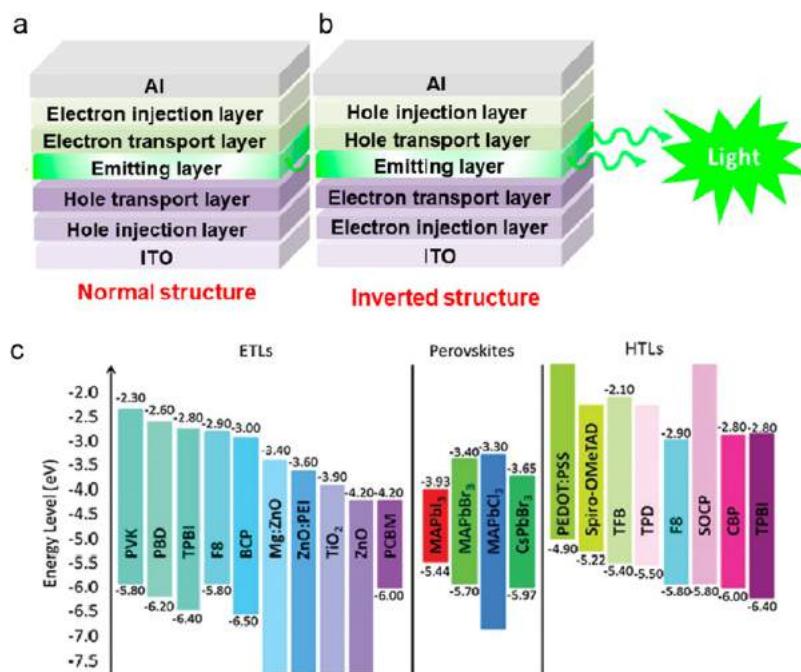


Figure 133. Device structures of perovskite LEDs. (a) Normal structure, (b) inverted structure. Reprinted with permission under a Creative Commons CC BY license from ref 1202. Copyright 2018 MDPI. (c) Energy level alignment of various materials used as perovskites, ETLs, and HTLs in the reported HPLEDs. Reproduced with permission from ref 1201. Copyright 2017 Elsevier.

Color of LHP Emitters. Normally, the EL spectra of LHP-LEDs are almost same with the photoluminescence spectra of adopted LHP emitters, with band gap being predominately determined by the halogen species.^{1126,1157,1174} For the LHPs with single halogen species, three discrete and narrow emissive bands with a width of around 20–30 nm go across the whole visible range, which means almost the whole color gamut is covered.^{14,443,1175} However, except the green bromine-based LHPs, the near-ultraviolet chlorine-based and near-infrared iodine-based LHPs are too extreme for most application of LEDs.^{78,1092,1173} Using alloyed halogen species, the emissive band of the resulting LHPs can be tuned across the whole visible range; correspondingly, their color gamut is also extended.^{78,1083,1092,1173} However, compared to the single halogen species LHP-LEDs, the EL spectra of LHP-LEDs based on alloyed halogen species LHP emitters demonstrate an irreversible shift because of the migration of halogen anions and vacancies under an applied electric field.^{1078,1099,1142,1171} To date, LEDs using single halogen species emitters, especially the APbBr₃ green ones, still dominate the development of LHP-LEDs by virtue of high EQEs over 20% and high device operation stability.^{404,1079} As the last piece of LHP-LED jigsaw in the prospective full-color display applications, the progress of blue LHP-LEDs is still lagging behind the red and green ones, because of a low luminous efficiency and poor stability of chloride-based blue LHP emitters.^{1067,1083,1096} Alternatively, APbBr₃ NPs and other nanostructures with a strong quantum confinement are held in great consideration as prospective blue emitters in LHP-LEDs.^{216,899,1082,1113,1177}

Dimension of LHP Emitters. Because of a low exciton binding energy (around dozens of meV), most excitons generated by photon excitation or electrically driven in bulky LHPs would dissociate into free charge carriers, leading to a low efficient radiative recombination.^{894,896,1133,1178,1179} Also, trap-assisted nonradiative recombination in polycrystalline LHPs with high density of defects additionally competes

with the radiative processes.^{1178,1180–1182} Nanocrystalline LHP grains with dimension less than 10 nm, *e.g.*, quantum dots, quantum well and NPs, confine charge carriers in a small volumen, and this enhances exciton binding energy to hundreds of meV and facilitates exciton radiative recombination.^{60,1178,1179,1183} Moreover, the surface defects of nanocrystalline LHPs can be passivated effectively using long-chain molecule ligands. Quasi-2D LHP NPs with a strong quantum-confinement shift the emission toward high energy even by 200 meV compared to their 3D NCs counterparts.^{60,1183} By varying the number of [PbX₆]⁴⁻ octahedral layers in these APbBr₃ NPs, their emission color can be adjusted from green to deep-blue, providing an alternative pathway for blue LHP-LEDs (Figure 132a).^{18,216,398,1102} Synthesis approaches have achieved a level of control such that NPs narrow thickness distributions and characterized by narrow emission spectra, can be prepared.^{60,216,398,747,1102} The presence of long alkyl chain spacers, confers also excellent stability against ambient moisture but on the other hand it blocks the injection of charge carriers into the NPs.^{49,1184–1186}

Deposition of LHP Emitter Films. The emissive films of most LHP-LEDs are deposited by solution processing, especially the organic–inorganic hybrid ones, which mainly includes *ex-situ* deposition using a prepared nanocrystalline LHP colloidal solution and *in situ* deposition using precursor solution.^{404,1078,1079,1082,1187} For the former, the synthesized high-quality nanocrystalline LHP, *e.g.*, NPs, is dispersed into a low polarity solvent, *e.g.*, toluene or tetrahydrofuran, to form a uniform colloidal solution for subsequent film deposition.^{1078,1079,1187} Normally, the concentration of these colloidal solutions must be high enough to deposit a continuous and uniform LHP film. In the meanwhile, to get a good charge carrier transport of the deposited LHP film, the amount of insulating long-chain ligands is kept at a low level, although leads to a poor stability of these colloidal solution, especially the NPs because of their propensity of self-assembly into

stacks.^{60,1129} By changing the preferred orientation of LHP-NPs into random or using a semiconductive molecular spacer, the emission from the resulting LEDs can be improved.^{1184,1188} For the latter, all precursors are resolved in a polar solvent, *e.g.*, dimethylformamide or dimethyl sulfoxide, to form a uniform solution for film deposition.^{398,1082,1121} Generally, an anti-solvent crystallization treatment using a low polarity solvent, *e.g.*, toluene, or solution is adopted during the film deposition.^{189,385,1082,1084} Moreover, an annealing post-treatment of the deposited LHP film is also required to enhance the quality of LHP films.^{189,385,1082,1084} In addition to solution processing, inorganic CsPbX_3 film can also be deposited by vacuum thermal evaporation. However, in this case the polycrystalline film that is obtained has high density of defects, without an effective spatial confinement of excitons and charge carriers, and exhibits a much lower emissive efficiency compared to the solution processed films prepared with surface-passivated nanoscale emitters.^{1189–1192}

Device Structures and Fabrications. The guideline of device structure design and fabrication of LHP-LEDs are developed within the framework originating from OLEDs and limited by the deposition of emissive layer, thus the device structures of most LHP-LEDs are simple. Normally, an LHP-LED contains multilayer thin films with a total thickness of around 100–200 nm sandwiched by two planar electrodes. Like other soft emitters, except rigid ITO glass, LHPs also demonstrate a good compatibility with flexible substrates.

Device Structures. To avoid the near-field quenching caused by electrode, in most LHP-LEDs a conductive poly(3,4-ethylenedioxythiophene):polystyrenesulfonate (PEDOT:PSS) film is selected as a spacer, which also can enhance hole injection from ITO anode (Figure 132b and Figure 133a,b).^{404,1078,1082,1187} In principle, the metallic PEDOT:PSS film is also regarded as an exciton quencher because of its highly electrical conductivity and interfacial defects.^{1078,1193} Therefore, an organic semiconductor film, *e.g.*, poly(4-butylphenyldiphenylamine) (poly-TPD), with low density of charge carriers is adopted as a buffer layer to eliminate the exciton quenching caused by PEDOT:PSS.^{396,1078} Moreover, this organic hole transport film is supposed to enhance hole injection into the recombination zone because there is a large mismatch between the deep valence band of LHPs and the Fermi level of PEDOT:PSS.^{396,1078,1082,1109}

To get a high EQE, a balanced charge carrier injection into the recombination zone is essential. In LHPs, holes and electrons have comparable mobilities, which helps to achieve a balanced charge carrier in LHP-LEDs.^{11,1187,1194} With consideration of the high conductivity of PEDOT:PSS, therefore, a high mobility/conductivity electron injection/transport layer, *e.g.*, 2,2',2"-(1,3,5-benzenetriyl)-tris(1-phenyl-1*H*-benzimidazole) (TPBi), is required to ensure a balanced charge carrier injected into the LHP layer.^{396,1078,1082,1187} For the cathode, a thermal evaporating deposited aluminum film with a buffer layer, *e.g.*, lithium fluoride or caesium carbonate, is a popular choice.^{396,1078,1082,1187} Additionally, ITO can also work as cathode to in an inverted structure device.^{1079,1195–1197} Correspondingly, some functional layers were also required for a balanced charge carrier injection. Normally, a n-type semiconductor film, *e.g.*, zinc oxide NCs, can be selected as matched electron transport layer.^{1079,1195–1197} Drawing inspiration from the PEDOT:PSS/poly-TPD combination used in normal structure devices, a polymer film, *e.g.*, polyethylenimine ethoxylated, is

required to modify ZnO NC film before the deposition of LHPs.^{1079,1195–1197}

Without the limitation of solution processing deposition, in principle, an LHP-LED with more advanced device structure can be achieved using vacuum thermal evaporating deposition. Even in most solution processed LHP-LEDs, the deposition of metal electrode and other organic functional layers still need a vacuum thermal evaporation. In particular, using current solution processing technology, it is almost impossible to get a large-scale uniform emissive film with fine structure pattern for a LED display.

Device Fabrication. Generally, the solution processing deposition used for LHP films in LHP-LEDs includes spin-cast, inkjet printing and slot-die coating technologies.^{1176,1187,1198} So far, spin-cast is the most popular technology used for the solution processing film deposition in various soft material LED fabrication, including LHP-LEDs, QLEDs, and polymer LEDs.

At a practical level, for solution processing film deposition, the compatibility of film deposition plays a critical role in fabricating a successful LHP-LED. Normally, it is required that the surface energy of the deposited film must be higher than that of the solution used for subsequent film deposition. To increase the surface energy of polymer film, a charging treatment of oxygen plasma can be adopted. This however leads to the formation of surface defects that would increase the nonradiative recombination of emitters. Moreover, the deposited films are required to be highly passivated to withstand the solution processing of subsequent LHP film deposition. For example, with an annealing post-treatment, the passivation of poly-TPD and ZnO NC film is improved against subsequent solution processing on them.^{396,1078,1079,1082,1109,1195–1197} Because of their ionic crystal structure, LHPs are sensitive to high dielectric constant environment. For this reason, any processing of highly polar solvents onto LHPs are excluded from device fabrication.^{1078,1199,1200} Other functional layers, including top electrode, can also be deposited using solution processing deposition; however, their device reliability is not as good as the thermal evaporated ones.

For inorganic CsPbX_3 LHPs, the films can also be deposited by a coevaporation of two precursors CsX and PbX_2 or CsPbX_3 in a high-vacuum chamber.^{1189–1192} The whole device, except some solution processing functional layers, *e.g.*, PEDOT:PSS, can be deposited in a single run without breaking the vacuum, which is helpful to eliminate any potential negative influence caused by the atmosphere in the glovebox. In principle, the uniformity of LHP film and the reliability of resulting LEDs fabricated using the vacuum thermal evaporating are higher than those of the corresponding devices fabricated using solution processing technologies, especially in large-scale film deposition. Commonly used electron transport layers and hole transport layers with their corresponding energy levels are summarized in Figure 133c.¹²⁰¹

Luminous Efficiency Drop. A high EQE means a maximized output of photon number with respect to a minimized input of electrons number injected into devices, mainly including three factors for LHP-LEDs:

$$\text{EQE} = E_{\text{in}} \cdot E_{\text{eh}} \cdot E_{\text{rad}} \cdot E_{\text{out}} \quad (4)$$

In the expression above, E_{in} is the charge carrier balance factor in the recombination zone, and these injected charge carriers will form excitons with a possibility of E_{eh} . The factor E_{rad}

depicts the fraction of the intrinsic radiative efficiency of emitters, normally, which is equivalent to the PLQY of LHP emissive film. Though the emission of LHPs originates from exciton radiation, due to a strong spin–orbit coupling caused by heavy lead atoms, this electron transition obeys the conservation of total momenta rather than spin statistics.¹⁴⁷ The last E_{out} determines the photon extraction efficiency of the device, which is dependent on the device structure and can be defined as $1/(2n^2)$ (n is the refractive index of films).

If all charge carriers injected through electrode flow into the recombination zone, the E_{in} will be unity. EQE loss related to E_{in} is caused by leakage currents which depends on device structure and quality. In a low-quality device containing a large number of pinholes and trap states, the injected charge carriers would flow across the device *via* this bypass instead of being injected into the recombination zone. Due to an effective spatial confinement of nanocrystalline LHP domains, the charge carriers injected into the recombination zone will meet each other with a high possibility E_{eh} and form stable excitons. In a high driving current density level, the injected charge carriers would pass through the device without recombination as an overflow current, resulting in a drop in E_{eh} and EQE, which can be supposed to be another origin of leakage current.¹¹⁸⁷

The factor E_{rad} plays a dominating role in determining EQE of LHP-LEDs. At a low excitation intensity level, a trap-mediated nonradiative process dominates the exciton recombination, which is consistent with the low initial value of luminous efficiency, thus a high-quality LHP emissive film with a low density of defect is essential.^{1187,1203–1206} By increasing the excitation intensity, the exciton radiative recombination will dominate the trap-mediated process.^{1187,1203,1205,1206} A further increase of excitation intensity will result in a multiexciton Auger nonradiative process and luminous efficiency droop (Figure 132c).^{1187,1203,1205,1206} In the electrically driven devices, the injected charge carriers, especially the excess ones caused by imbalanced injection, will increase the probability of Auger nonradiative recombination even at a low driving current density level (Figure 132d).^{1187,1207}

For almost of all planar multilayer structure LEDs, including OLEDs and QLEDs, most generated photons will be trapped inside devices by waveguide mode and substrate mode, only around 15–20% photons can be outcoupled because of the refractive index mismatch among functional layers, glass substrate and air.^{1187,1208} Similar to that with OLEDs, E_{out} can be enhanced using periodic nano- or microstructures, *e.g.*, microlens array in this kind of multilayer planner structure LEDs.¹²⁰⁹ Moreover, because of the overlap between absorption and luminescence spectra, which means an equivalently prolonged lifetime of excitons, the photons trapped inside device should have more chance to escape before annihilation by a recycling process.¹¹⁴⁰

In the working state of LHP-LEDs, one more factor that can result in EQE drop is the degradation of LHPs emitters caused by a considerable ion migration, which can be facilitated by applied electrical field and evidenced by a hysteresis dependence between driving current density and driving voltage in almost all electrooptic applications based on LHPs.^{956,1210}

Stability of LHP-LEDs. Device operation stability is a very important consideration when evaluating a LED at a practical level, and achieving a good stability is still a severe challenge for LHP-LEDs.^{98,469,956,1099} Although LHP-based LEDs have a similar device structure to QLEDs the degradation is faster,

and the degradation mechanisms may relate to the perovskite, as well as the interfaces between the perovskite and carrier injection layers. In general, the degradation mechanisms of perovskite LEDs are divided into four categories: (a) Ion migration, (b) interactions with surrounding moisture and oxygen, (c) electrochemical reactions, and (d) interfacial reactions.¹²¹¹ Ion migration of halide ions in PeLEDs is intrinsically a defect migration process which is strongly related to perovskite surface chemistry and defects.⁸⁶ It leads to defect creation (*e.g.*, Frenkel defects), halide vacancy migration and lattice distortion which are detrimental to spectral stability and material stability. Halide ion migration can occur both within the perovskite emitting layer^{1079,1212} and across the organic transport layers.^{1190,1213} In addition, LHPs are sensitive to moisture, thus high-quality encapsulation is required for protecting the device against the environment.^{98,469,956,1088,1099} The heterostructure of 2D LHP-NPs and matrix-dispersed nanoscale LHPs can suppress ion migration effectively and provide additional protection for LHP emitters against environmental moisture.^{189,398,1079,1189} Moreover, as current-driven devices, the structural instability induced by mechanical stress is also a severe challenge for LHP emitters because of their ultralow thermal conductivity and Joule heating generated by devices under operation.^{244,1214–1216} Electroluminescence spectral stability is another challenge for colloidal perovskite LEDs, especially for deep blue (~465 nm) and pure red (~625 nm) emitters.¹²¹⁷ The instability of the EL spectra is primarily due to the halide segregation. Apart from ion migration, electrochemical reactions between migrated species from the perovskite and electrodes is another degradation pathway during device operation. Yuan *et al.* showed in bulk thin film MAPbI₃ under electrical bias, the perovskite can react with electrodes to form I₂ gas and PbI₂, which makes the degradation process irreversible.¹²¹⁸ The interaction between the perovskite layer and transport layers can take place without external electrical bias, for example, the acidic nature of PEDOT:PSS layer can cause reactions with ITO over time upon direct contact, and the etched Sn and In ions can diffuse into perovskite layers and act as traps.¹²¹⁹ To suppress ion migration (halide segregation) and interfacial interactions, there are many methods that have been reported, such as compositional engineering, dimensional engineering, and defect passivation at NC surface and interfaces between the emitting and injection layers.⁴⁹ However, currently, there is no individual strategy that can passivate all defects and suppress device degradation. It is critical to understand and utilize multiple strategies to further improve the stability of PeLEDs.

Summary and Outlook for Perovskite LEDs. LHP-LEDs have achieved incredible progress over the past few years, with excellent features, including highly efficient light emission, high-color purity, ultrawide color gamut, low cost of raw materials and fabrication methods, as well as good compatibility with existing OLEDs/QD-LEDs manufacturing technologies. In recent years, OLEDs, QD-LEDs, micro-LEDs, and other screenless display technologies are competing with each other. In particular, the great similarity between LHP-LEDs and CdSe QD-LEDs from device fabrication procedures to output features in a working state suggests a strong exclusiveness as prospective applications.

However, before evolving into practical products, LHP-LEDs need to overcome some critical bottlenecks, such as the concern of the toxic lead atoms, poor operation stability and large-scale panel fabrications, which has been attracting great

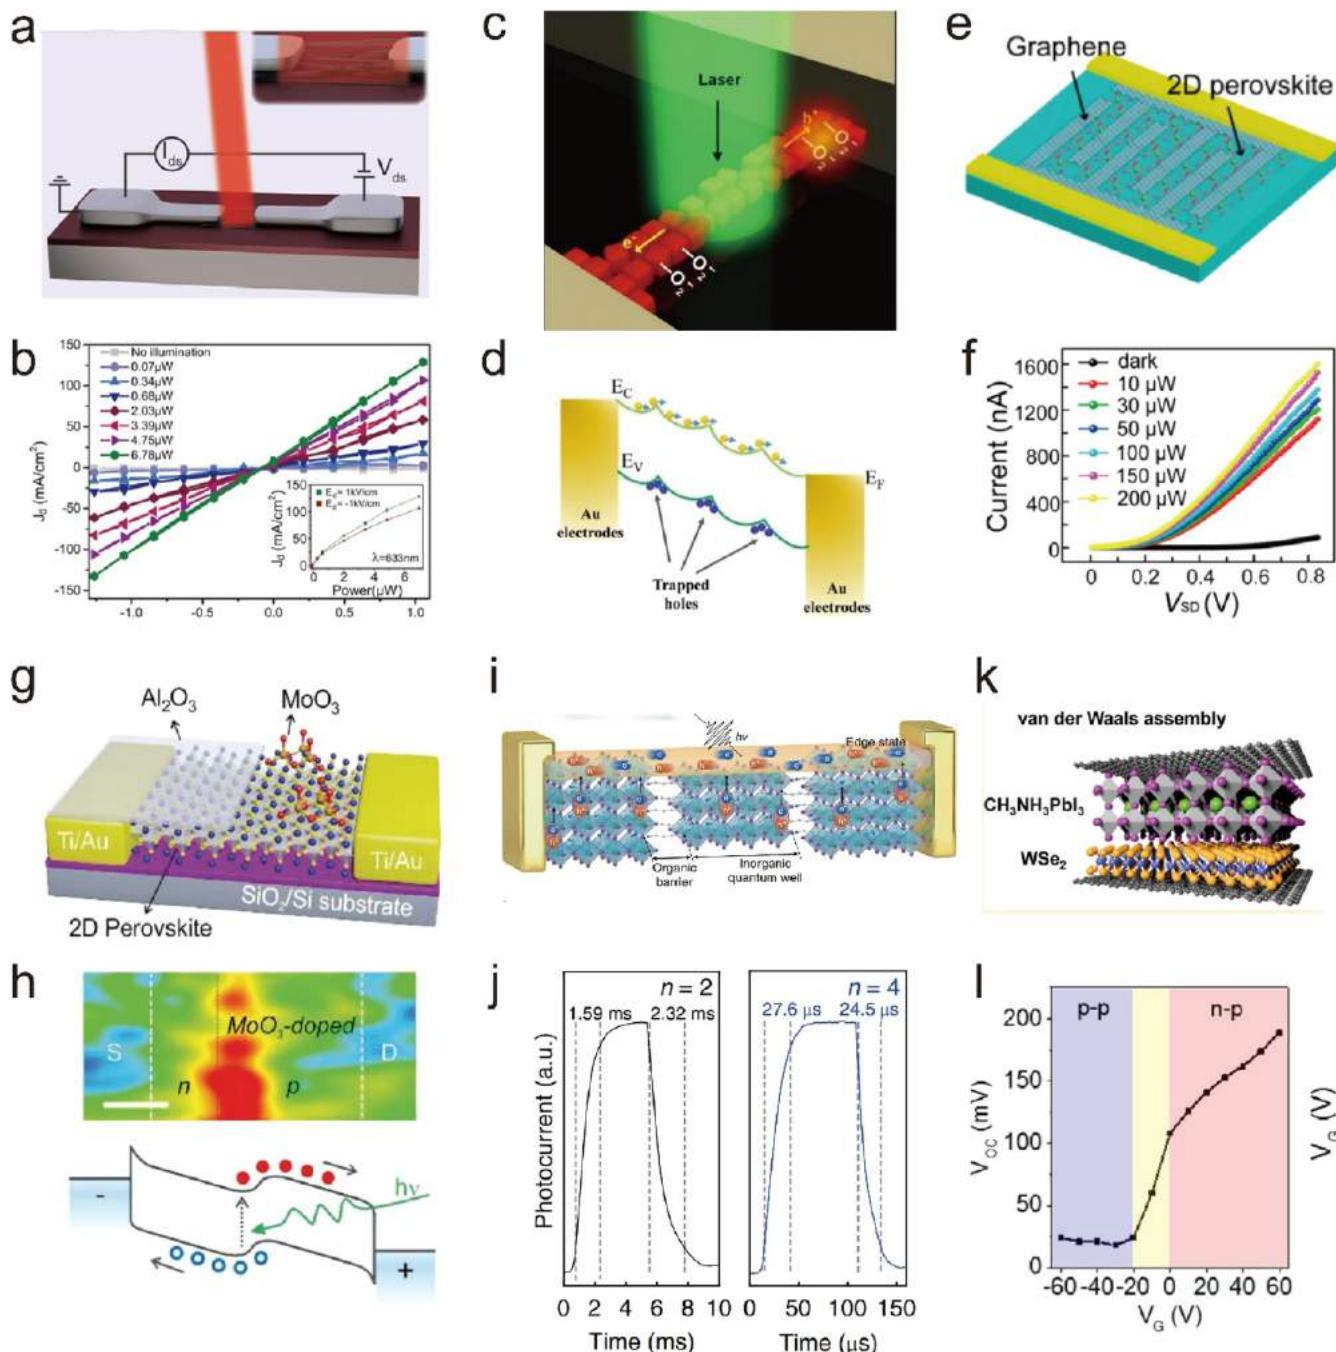


Figure 134. Photodetectors and field-effect transistors based on perovskite NCs. (a) Schematic diagram of 1D MAPbI_3 wire photodetectors and (b) I – V curve of the MAPbI_3 wire photodetectors under irradiation with laser wavelength of 633 nm. Reproduced from ref 1228. Copyright 2014 American Chemical Society. (c) Schematic diagram of 1D aligned CsPbX_3 NCs photodetectors and (d) schematics of carrier dynamic in perovskite 1D NCs photodetectors under illumination. Reproduced with permission from ref 1232. Copyright 2019 Royal Society of Chemistry. (e) Schematic diagram of 2D perovskite/graphene photodetectors and (f) I – V curve of the 2D $(\text{C}_4\text{H}_9\text{NH}_3)_2\text{PbBr}_4$ /graphene heterostructure photodetectors in the dark and under various illumination intensities with a 470 nm laser irradiation. Reproduced from ref 1233. Copyright 2016 American Chemical Society. (g) Schematic MoO_3 -doped 2D perovskite nanosheet photodetector and (h) photogenerated current mapping in source–drain channel and schematic band diagram under $V_d = +1$ V under irradiation. Reproduced with permission from ref 1234. Copyright 2018 John Wiley & Sons, Inc. (i) Schematic diagram carrier dynamics in the single-crystalline (101)-oriented layered perovskite photodetector and (j) photoresponse of 1D-layered perovskites array with $n = 2$ and 4. Reproduced with permission from ref 1235. Copyright 2018 The Authors. (k) Schematic of $\text{CH}_3\text{NH}_3\text{PbI}_3/\text{WSe}_2$ heterojunction field transistor and (l) The V_g – V_{OC} curve extracted from source and drain channel in $\text{CH}_3\text{NH}_3\text{PbI}_3/\text{WSe}_2$ heterojunction at 77 K. Reproduced from ref 1236. Copyright 2015 American Chemical Society.

attention, and some impressive progress has been achieved thus far. Until now, the performance of the lead-free perovskite-inspired materials have lagged behind the performance

of their lead-based counterparts. The operational stability of LHP-LEDs is also a complicated issue because the device contains multilayer thin films and resulting heterogeneous

interfaces. The extrinsic factors, including oxygen, moisture, *etc.* caused by ambient environment, can be fixed by following the well-established programs developed for OLEDs. The degradation of LHP emitters should be intrinsic among all possible factors, especially, which can be accelerated by applied electrical current and field in LEDs. The large-scale panel manufacturing is not an exclusive problem of LHP-LEDs, which also challenges for other solution processing LEDs, such as QD-LEDs and polymer LEDs. A nanoscale uniformity of all functional films contained in the LHP-LEDs is essential, because the pinhole and any other nonuniform morphology will lead to a highly deviated distribution of electric current flow and resulting brightness. A LHP-LED demo with spot size of square millimeters can be fabricated simply using spin-cast. However, when the spot area is increased to square centimeters level and even larger size, the deposition of such a large area film with a nanoscale uniformity is almost impossible using current technologies, including spin-cast, inkjet printing, *etc.*

Thus far, most works on LHP-LEDs have focussed on the enhancement of characteristic parameters, especially EQEs, at the technical level, however, the understanding of such enhancements are chained to the framework borrowed from OLEDs and QD-LEDs to a great extent. Actually, the performance enhancements of LHP-LEDs seem to have plateaued in the past years. Therefore, more fundamental work on LHP-LEDs is required for a better understanding of the working mechanism of such a contemporary LEDs. This would provide a guideline for the device works at the technical level and trigger a breakthrough in the device performance improvement in the future. For example, the above-mentioned stability issue of LHP-LEDs, though the same LHP emitters demonstrate a great stability under optical excitation, even in ambient atmosphere.

Photodetectors and Field-Effect Transistors. Photodetectors convert light signals to electrical signals, which is critical for a diverse range of applications, such as sensors and optical communication devices.¹²²⁰ Lead-halide perovskites are promising materials for photodetectors with high figure-of-merit (*e.g.*, responsivity and temporal response) owing to their strong optical absorption, high quantum efficiency, and ultralong carrier diffusion length.^{994,1221,1222} The initial reports on perovskite photodetectors were based on polycrystalline film, which indicates highest photoresponsivity of $\sim 3.5 \text{ A W}^{-1}$ at 365 nm in the range of visible to the near-infrared region.¹²²³ However, owing to polycrystalline structure, numerous crystal boundaries and defects exist in the perovskite film, which would serve as recombination and scattering centres in carrier dynamics, limiting the performance of the perovskite-based photodetectors.^{1223,1224} Low-dimensional perovskite NCs including nanocubes, nanowires, nanorods (1D), and nanosheets (2D) have recently been developed and tested for high-performance photodetectors. In particular, it has been demonstrated that lower defect density can be achieved than in their 3D counterparts, such as through surface passivation.

Fully inorganic CsPbX_3 QD-based photodetectors have achieved high photocurrent on/off ratios of over 10^5 , thereby enabling effective switching.³⁷ In order to increase the performance of the inorganic perovskite NC photodetectors, Kwak *et al.*¹²²⁵ and Wang *et al.*¹²²⁶ introduced conductive graphene as charge transport channel to enhance charge transfer, reaching a responsivity over $\sim 10^8 \text{ A W}^{-1}$. However, in

general, perovskite NCs are coordinated with long-chain organic ligands, which could hinder charge transport and therefore lead to slow photoresponses ($> 1 \text{ s}$). With regard to fast carrier dynamics, it is crucially important to optimize ligand molecular and device configuration. In this framework, conductive nanonets made of carbon nanotubes (CNTs) in CsPbBr_3 QD/CNT composites were used to improve charge extraction and transport, by which fast-response photodetectors with rise time of 0.016 ms have been achieved.¹²²⁷

Up to now, there have only been a few reports of MAPbI_3 -based photodetectors due to the limited stability of MAPbI_3 .⁴⁷⁸ However, 1D solid hybrid organic-inorganic perovskite NCs remain attractive as efficient carrier transport channels in photodetectors. Figure 134a,b presents the perovskite photodetectors based on solution-processed 1D MAPbI_3 NWs with a responsivity of 5 mA W^{-1} and a response time of $\sim 0.3 \text{ ms}$.¹²²⁸ However, the defects and grain boundaries in MAPbI_3 NWs lead to scattering effects which significantly reduces the responsivity. The defect density in MAPbI_3 NWs was reduced by surface passivation through OA soaking treatment.¹²²⁹ As a result, larger responsivities (4.95 A W^{-1}) and a shorter response times ($< 0.5 \text{ ms}$) were achieved. To further enhance the photodetector performance, Deng *et al.* developed a blade solution-casting method to increase the crystallinity of MAPbI_3 NWs.¹²³⁰ As the blade moves against the MAPbI_3 solution on the substrate, MAPbI_3 precipitates out at the triple-phase (solid–liquid–solvent vapor) interface upon solvent evaporation and continues to self-organize to form 1D NWs along the direction in which the blade moves. The as-fabricated MAPbI_3 NW photodetector possesses a high responsivity over 13 A W^{-1} due to the high perovskite crystal quality. Therefore, well-controlled gas–liquid–solid triple-phase contact within prepatterned substrates could be a key factor to produce large-scale high-quality NW crystals and practical perovskite NW photodetectors. Feng *et al.* developed a template-assisted method for the production of well-aligned single-crystal CsPbBr_3 NW arrays, which enabled a surprisingly high responsivity of $\sim 1400 \text{ A W}^{-1}$.¹²³¹ Dai *et al.* introduced an oxygen-related hole trapping state on the surface of the NCs, causing surface band bending, which results in an internal electric field that can spatially separate the photogenerated electron–hole pair, thereby suppressing the carrier recombination, as shown in Figure 134c,d. Additionally, polarized light detection can be achieved in the photodetectors based on the strict alignment of CsPbBr_3 NW arrays along the [100] orientation.¹²³¹ All these pioneering works clearly demonstrate the potential of perovskite NCs in the fabrication of efficient photodetectors.

High-quality 2D perovskite NCs have been considered to be effective photoactive media for high-performance photodetectors due to their large surface area to volume ratio and potential integration with other 2D materials and conventional silicon circuits.¹²³⁷ Essentially, there are two major working principles for photodetectors based on 2D perovskite NCs, *i.e.*, photoconductive and photovoltaic effects. A typical structure for perovskite photoconductors involves the perovskite sandwiched between two gold electrodes. 2D perovskite photoconductors typically deliver a responsivity of 22 A W^{-1} under visible laser illumination, which is superior to those photodetectors based on 3D perovskite films.¹²³⁸ The integration of 2D perovskites with other 2D conductive materials can be an efficient approach to improve photodetector performance. In particular, heterostructure photo-

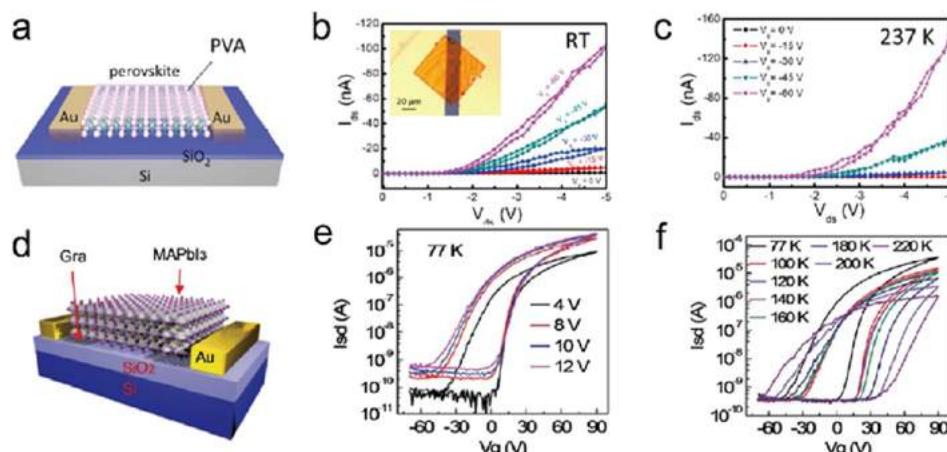


Figure 135. Perovskite NC-based FETs. (a) Schematic illustration of CsPbBr_3 -based FETs fabricated using the dry transfer method. Output characteristics of the as-fabricated CsPbBr_3 FETs under gate voltages in the range from -60 to 0 V at (b) room temperature and (c) 237 K. Reproduced from ref 1245. Copyright 2017 American Chemical Society. (d) Schematic illustration of the graphene-contact MAPbI_3 microplate-based FETs. (e) Transfer characteristics of the as-fabricated MAPbI_3 FETs under source-drain bias of 10 V at different temperatures from 77 to 220 K. Reproduced with permission from ref 1249. Copyright 2016 John Wiley & Sons, Inc.

detectors consisting of 2D perovskite ($\text{C}_4\text{H}_9\text{NH}_3)_2\text{PbBr}_4$ and interdigitated graphene electrodes were demonstrated, as shown in Figure 134e,f, in which graphene would be favorable for transporting photocarriers and improving stability in air.¹²³³ This device gives a high responsivity of 2100 A W⁻¹.¹²³³ For devices operating based on the photovoltaic effect, one or more junctions are normally required. In this regard, Ou *et al.* fabricated a lateral junction by partially doping the n-type pristine perovskite nanosheet.¹²³⁴ A large depletion region with a few micrometers width formed in which a lateral built-in electric field facilitates the separation and transport of photogenerated carriers. As a result, these photodetectors have a responsivity of ~ 1.42 A W⁻¹ and an EQE of $\sim 3.93\%$ at zero bias, much higher than those of the pristine 2D perovskite device. A single-crystalline 2D Ruddlesden–Popper perovskite nanowire with a pure (101) crystallographic orientation has been used to fabricate ultrasensitive photodetectors, as shown by Figure 134i.¹²³⁵ The organic layers act as insulating barriers which significantly reduce the dark current, whereas exposed crystalline perovskite layers function as charge conductive pathway for exciton dissociation, free-carrier conduction and charge injection, therefore giving an averaged responsivity of over 10^4 A W⁻¹ and a detectivity of over 7×10^{15} Jones. Apart from using dopants, the combination of 2D perovskites with other 2D semiconductors could also create a built-in electric field to form a p-i-n junction.^{1236,1239} A graphene/WSe₂/2D MAPbI_3 /graphene device was assembled to work as a photodetector with ultrahigh on/off photocurrent ratios ($>10^6$) under negative bias.

Beyond photodetectors, the distinctive gate-modulated features due to the ambipolar nature of 2D perovskites under different biases underpin their great promise for transistors. The reported mobilities of hybrid perovskite film-based transistors are mostly below 1 cm² V⁻¹ s⁻¹, which are much lower than their high intrinsic mobility ~ 200 cm² V⁻¹ s⁻¹ due to unavoidable ion migration at room temperature.^{1240–1244} In this regard, these results would suggest that perovskite NCs with lower ion vacancy and grain boundary density are promising for achieving improved performance. As shown in Figure 135a–c, Huo *et al.* developed

high-quality ultrathin boundary-free CsPbBr_3 platelets using van der Waals epitaxy and dry transfer processes, yielding FET hole mobilities of 0.32 and 1.04 cm² V⁻¹ s⁻¹ at room temperature and 273 K, respectively.¹²⁴⁵ Yu *et al.*¹²⁴⁶ further enhanced surface adhesion between thin single-crystal MAPbX_3 and prepatterned FET substrates to reduce surface contamination, reaching record electron and hole mobilities of 1.5 and 4.7 cm² V⁻¹ s⁻¹ at room temperature, respectively. Moreover, Cheng *et al.*¹²³⁶ systematically investigated transport properties of the high-quality perovskite materials with van der Waals contacts such as graphene and gold.^{1236,1247–1249} As shown in Figure 135d,e, Li *et al.* demonstrated temperature-dependent transfer characteristics of graphene-contact MAPbI_3 microplate-based FETs with estimated electron mobilities of 4 cm² V⁻¹ s⁻¹ at 77 K.¹²⁴⁹ However, by achieving atomically flat contacts, the as-fabricated CsPbBr_3 FETs showed Hall mobilities >2000 cm² V⁻¹ s⁻¹ at 80 K and ultralow bimolecular recombination coefficients of 3.5×10^{-15} cm³ s⁻¹.¹²⁴⁷ Improving contacts with electrode and dielectric layers in FETs would be effective strategies to increase the performance of the perovskite NC-based FETs. However, exploration of perovskite NCs with lower ion vacancy densities will be essential for achieving practical FETs.¹²⁵⁰

Beyond visible photodetectors and FETs, metal-halide perovskites are also promising candidates for the detection of high-energy ionizing radiation, such as X-rays and γ -rays. Radiation detectors with high sensitivities and small lowest detectable dose rates can potentially be achieved with low cost due to the solution processability of the metal-halide perovskites and their high-Z elements.^{1251–1253} For X-ray detectors, the ability to control charge carrier movement is key to their functionality. Charge generation, transport and separation all must occur in the perovskite NCs sequentially upon X-ray irradiation.^{1254,1255} In particular, favorable optoelectronic properties, such as strong absorption, tunable band gap, long carrier diffusion length and large bulk resistivity in lead-halide perovskite NCs also contribute to improved sensitivity.¹²⁵⁶ Figure 136a shows the linear X-ray attenuation coefficient of different materials, suggesting that the perovskite

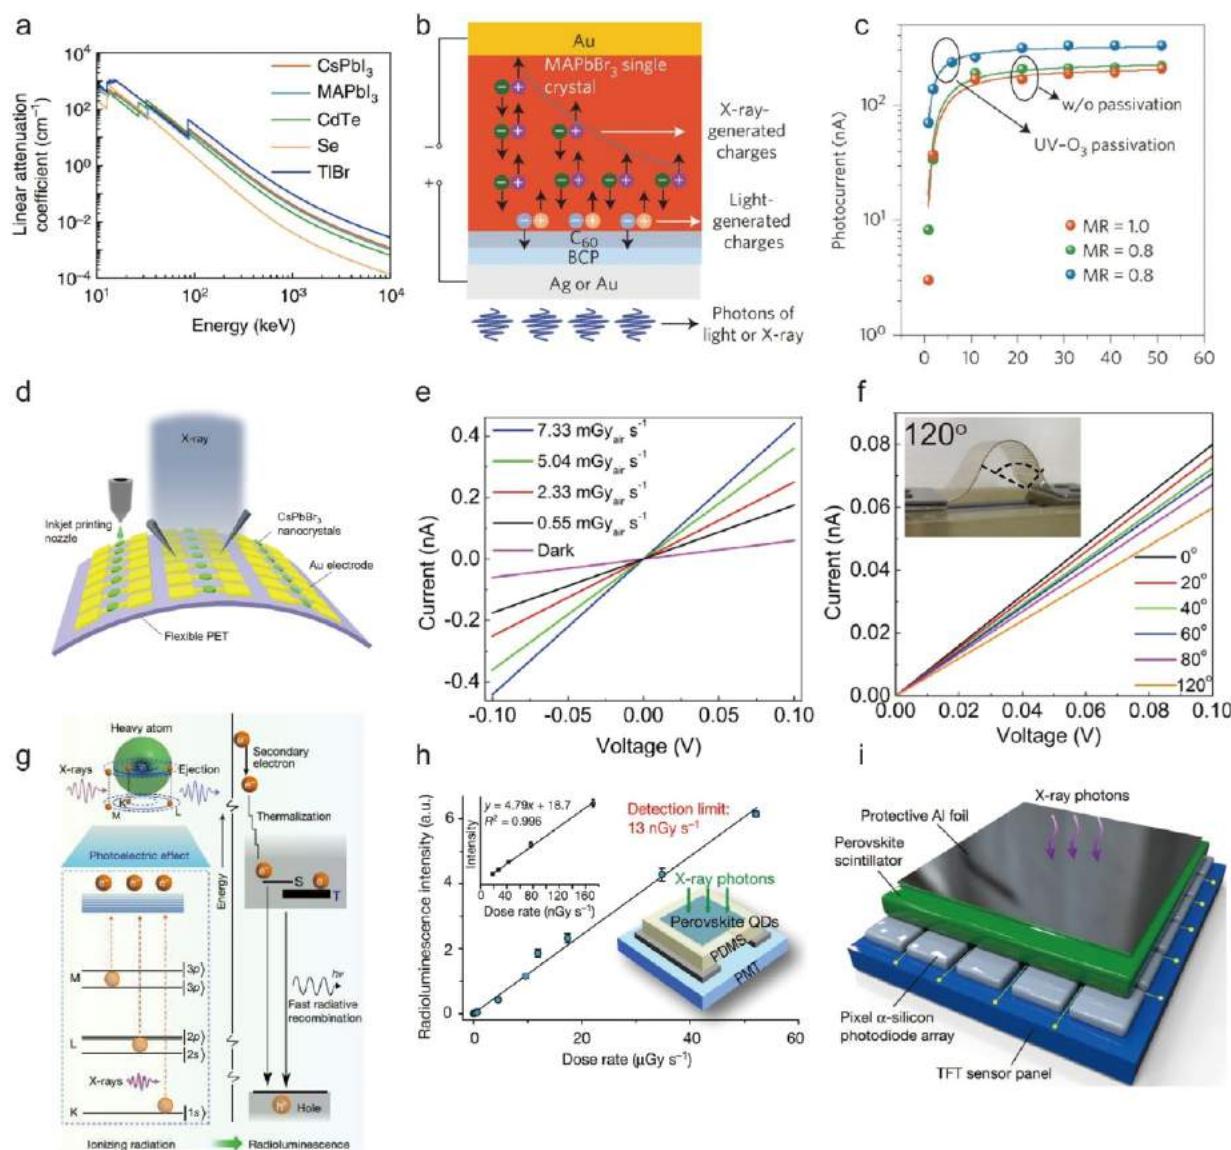


Figure 136. High-energy ionizing radiation detectors based on perovskite NCs. (a) Linear attenuation coefficient of MAPbI₃, MAPbBr₃, CdTe, Se, and TiBr in the 10–10000 keV energy range. Reprinted with permission under a Creative Commons CC BY license from ref 1255. Copyright 2019 The Authors. (b) Schematic configuration of the cross-sectional view of single-crystal X-ray detector. (c) Photocurrent of MAPbBr₃ single-crystal devices with different molar ratios and surface passivation procedure *versus* electrical bias. Reproduced with permission from ref 1257. Copyright 2016 Nature Publishing Group. (d) Schematic diagram of the flexible X-ray detector arrays based on inkjet-printed CsPbBr₃ NCs on PET substrate. (e) Dark current and photocurrent of the CsPbBr₃ NCs X-ray detectors under different X-ray dose rates with 0.1 V bias voltage. (f) *I*–*V* curves of the CsPbBr₃ NCs X-ray detectors at various bending angles with the X-ray irradiation of 7.33 mGy_{air} s⁻¹ and 0.1 V bias voltage. Reproduced with permission from ref 1258. Copyright 2019 John Wiley & Sons, Inc. (g) Hypothesis of working principle of a CsPbBr₃ NC-based X-ray scintillation. In general, photoelectric ionization, thermalization, and fast radiative recombination take place upon X-ray illumination in lead-halide perovskite NCs. (h) Radioluminescence intensity of a CsPbBr₃-based scintillator *versus* dose rate. The inset at the top left presents radioluminescence profiles in the low dose rate range. (i) Schematic illustration of a prototype CsPbBr₃ NCs-based flat-panel X-ray imaging system. Reproduced with permission from ref 1259. Copyright 2018 Springer Nature Limited.

materials are superior over current commercial materials for multiple solid-state applications.¹²⁵⁵

In general, X-ray detectors could be classified as semiconductor-based direct and scintillator-based indirect devices. Solution-processed MAPbI₃ films were initially used for X-ray detection by directly recording photogenerated current in both photovoltaic and photoconductive devices.¹²⁶⁰ Owing to the heavy Z elements (Pb and I), high X-ray sensitivity and ($\sim 25 \mu\text{C mGy}_{\text{air}}^{-1} \text{ cm}^{-3}$) and responsivity (1.9×10^4 carriers/photon) were demonstrated, which is superior to amorphous

a-Se-based X-ray detectors. Similar to visible photodetectors, the performance of X-ray detectors could be dramatically improved by interfacial engineering.¹²⁶¹ As shown in Figure 136b and c, using surface defect passivation processes, Wei *et al.* developed a hard X-ray detector using high-quality single-crystal MAPbBr₃, which would enhance charge extraction efficiency and therefore yield a high sensitivity ($\sim 80 \mu\text{C Gy}_{\text{air}}^{-1} \text{ cm}^{-2}$) and a lowest detectable dose rate ($\sim 0.5 \mu\text{C mGy}_{\text{air}}^{-1} \text{ s}^{-1}$) at near zero bias.¹²⁵⁷ The as-fabricated MAPbBr₃ X-ray detectors provide not only a four times higher X-ray sensitivity

but also \sim 100-fold reduction in the lowest detectable dose rate than a-Se-based X-ray detectors.¹²⁵⁷ Moreover, the record-high X-ray sensitivity could be further promoted up to \sim 50000 μ C Gy_{air}⁻¹ cm⁻² in thick hot-pressed CsPbBr₃ quasi-particle film with same crystal orientation and thickness of several hundreds of micrometers.¹²⁵³ Alternatively, interface engineering would be suggested as an effective way to minimize the dark current upon X-ray irradiation. Kim *et al.* demonstrated a spin-cast MAPbI₃-based X-ray detector comprising polyimide (PI)-MAPbI₃ layer as the hole-transporting pathway and PI-MAPbBr₃ as hole-blocking pathway, producing broad X-ray absorption range and a large sensitivity over 10 μ C mGy_{air}⁻¹ cm⁻².¹²⁶² Strategically, low-cost patterning perovskite NCs on flat or flexible substrates is of great importance for scale production of printable and flexible perovskite-based X-ray detectors. As shown in Figure 136b, Liu *et al.*¹²⁵⁸ demonstrated flexible soft X-ray detectors array based on CsPbBr₃ NCs film using inkjet printing. Apart from a reasonably high sensitivity at low X-ray dose rate (\sim 17.2 μ C mGy_{air} s⁻¹; see Figure 136e), the as-fabricated perovskite flexible devices only lose 25% electrical signal at bending angle over 120° (see Figure 136f) and sacrifice only 12% current after 200 bending circles.

Perovskite NC scintillators have also emerged as commercially competitive indirect converters for nondestructive X-ray detectors.^{1252,1263} Chen *et al.* demonstrated fully inorganic perovskite NC-based scintillators for X-ray imaging.¹²⁵⁹ Due to highly emissive triplet excited states, fast radiative recombination and high quantum efficiency from CsPbBr₃ NCs, the as-fabricated scintillators have a rapid response time of \sim 46 ns and a low X-ray detection limit of 13 nGy s⁻¹ (\sim 400 times lower than typical X-ray diagnostics), as indicated in Figure 136g,h.¹²⁵⁹ The as-fabricated prototype CsPbBr₃ NCs-based flat-panel X-ray imaging system is desired for dynamic real-time X-ray imaging when exposed to a low X-ray dose of 15 μ Gy, as shown by Figure 136i. In addition, very recent reports indicated that embedding emissive CsPbBr₃ NCs in host matrices such as Cs₄PbBr₆ and plastic waveguides is a very effective approach to produce stable and low optical loss scintillators for X-ray detectors.^{494,1264} Moreover, lead-free perovskites have also been used in the fabrication of X-ray detectors.^{1265,1353} For example, (C₈H₁₇NH₃)₂SnBr₄ 2D-layered perovskites with absolute near-unity PLQY and a large Stokes shift have been applied in scintillators for green X-ray imaging applications.¹²⁶⁵ In another work, Zhu *et al.*¹²⁶⁶ have demonstrated the scintillators based Cs₂Ag_{0.6}Na_{0.4}In_{0.85}Bi_{0.15}Cl₆ (PL lifetime = 1.3 μ s) with enhanced light yield of 39000 ± 7000 photons/MeV compared to that of perovskite colloidal CsPbBr₃ materials; however, the lead-free perovskite materials, in general, suffer from long decay time, which are required further material optimization. More importantly, most reported lead-free-based X-ray detectors are based on bulk single crystals or 2D-layered perovskites, whereas the corresponding NC-based devices are yet to be realized. In summary, the field of perovskite-based visible light and X-ray detectors is a very fast-moving research area toward the realization of various applications including integrated optoelectronic devices, sensing, and medical radiography. Among all, the scintillator-based indirect strategy is more promising in low-cost X-ray imaging system by combining current CMOS system and facile preparation methods.

Summary and Outlook on Perovskite Photodetectors. Owing to their strong attenuation of visible and high-energy

photons, high photoluminescence quantum yields and ambipolar charge transport, lead-halide perovskites have been demonstrated as promising photodetectors, FETs and X-ray/ γ -ray detectors. Among these applications, it has been shown that nanostructuring has delivered benefits in terms of performance or compatibility with flexible substrates. In photodetectors, perovskite NCs have demonstrated improved performance over 3D perovskite thin films through surface passivation to reduce nonradiative recombination. On/off ratios exceeding 10⁵ have been achieved in photodetectors based on CsPbX₃ NCs. Blending with conducting graphene or CNTs led to high responsivities of 10⁸ A W⁻¹ and fast response times of 0.016 ms by improving carrier extraction. Furthermore, by synthesizing CsPbBr₃ NWs that are well-aligned, responsivities as high as \sim 1400 A W⁻¹ have been achieved, as well as polarized light detection. Future improvements in performance will depend on careful control over the interfaces between the perovskite and contacts, as well as control over the distribution of organic ligands, which could reduce dark current but could also increase response times if placed inappropriately such that they reduce charge extraction.

The ambipolar nature of charge transport in lead-halide perovskites has been taken advantage of in FET applications. A key challenge is ion migration in perovskites, which modules the field-effect mobility to well below the intrinsic mobility. Grain boundary density, as well as interfaces with contacts play an important role. Future work should focus on improved contact and dielectric layers, as well as synthesis routes to reduce the density of vacancies to reduce ion migration.

Finally, the high average atomic number in lead-halide perovskites allows them to strongly attenuate X-ray and γ -rays, and an improved performance over industry-standard amorphous selenium has been demonstrated. Although full attenuation requires the use of thick single crystals, NC-based perovskites have been shown to demonstrate reasonable performance as solid-state X-ray detectors but with the added advantage of being solution processable on flexible substrates. CsPbBr₃ NCs have also been shown to be effective X-ray scintillators, owing to the high quantum efficiency, fast radiative recombination, and highly emissive triplet excited states.

Perovskite Nanocrystal Solar Cells. Lead-Halide Perovskite NCs. Lead-halide perovskites have brought about a revolution in thin film photovoltaics. In a similar manner, lead-halide perovskite NCs have very recently also brought about a revolution in QD solar cells.^{90,115,185,318,523,1267–1271} Perovskite NCs can utilize surface energy for improving phase stability, have different, but also low cost solution-based fabrication processes, and enable a platform to better understand and engineer the properties of MHPs, such as through molecular surface/grain passivation, achieving higher PLQY, formation of perovskite heterojunctions, *etc.*⁹⁰ Quantum confinement effects, while perhaps less pronounced than in the Pb chalcogenides, are still prevalent in Pb-halide perovskites, which have Bohr radii similar to those of Cd chalcogenides. Thus, perovskite NCs with relatively large diameters (>10 nm) are best characterized as in the intermediate confinement regime.^{1272,1273}

An interesting aspect of halide perovskite NCs is the role the surface energy plays in the stabilization of certain crystalline phases that are not stable in their bulk counterparts at room temperature. Perhaps a reason why researchers have broadly overlooked halide perovskites as a semiconductor system for

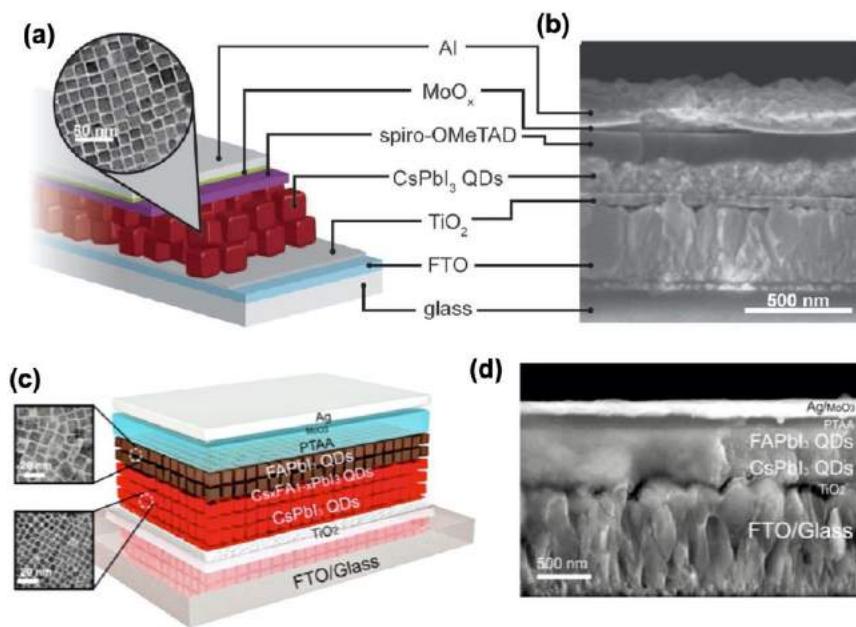


Figure 137. (a) Schematic of a perovskite QD solar cell with halide perovskite NCs as the light absorber and (b) corresponding SEM image of an exposed cross section. Reproduced with permission from ref 185. Copyright 2016 American Association for the Advancement of Science. (c,d) Schematic of a perovskite QD solar cell employing two compositions which have been shown to form a charge separating heterostructures (c) and the corresponding cross-sectional SEM image (d). Reproduced from ref 1283. Copyright 2019 American Chemical Society.

the past 80 years is the limited number of A-site cations needed to stabilize Pb-halides as a perovskite. Cs⁺ is typically too small to promote CsPbI₃ into the octahedral corner-sharing perovskite phase, and thus a slightly larger but uncommon organic cation, such as methylammonium, is required to achieve the tolerance factor needed to accomplish the perovskite structure. For the interest of single junction solar cells, a band gap as close as possible to 1.3 eV is preferred in order to maximize the potential efficiency as predicted by the Shockley–Queisser analysis.¹²⁷⁴ Thus, CsPbI₃, MAPbI₃, and FAPbI₃,¹²⁷⁵ are the most common conventional perovskite structures of which CsPbI₃ and FAPbI₃ are especially interesting. The former by the inorganic nature with higher temperature stability and the latter also presenting higher stability than MAPbI₃, and the narrowest band gap of 3D iodine perovskites. As stated above, pure composition CsPbI₃ and FAPbI₃ suffer from cations either too small or too large to preserve the stability of the photoactive perovskite black phase, converting into the less photoactive yellow phase at room temperature in bulk materials.^{185,1275,1276} However, by reducing the perovskite size to <20 nm, the contribution of the surface energy (namely tensile strain) can influence the stability of the phase, promoting the formation of the black perovskite phase of CsPbI₃ and FAPbI₃.^{185,1277,1278} Ironically, at the nanoscale, MAPbI₃ (with the most ideal A-site cation radius for bulk compounds) has the lowest stability.¹²⁷⁹ There are phase-related nuances of perovskite NCs where the transitions among the α , γ , and δ perovskite phase can be size, composition, and temperature-dependent.^{1273,1280}

Beyond phase stabilization of the building blocks needed for perovskite QD solar cells, the next challenge is preparing QD films thick enough to absorb incident light, while simultaneously having sufficient transport properties to harvest the photogenerated charges. Low polarity solvents such as methyl acetate (MeOAc) or ethyl acetate (EtOAc)^{185,1281} preserve the

stability while removing or replacing surface ligands¹²⁸² and have permitted the early report on perovskite NC solar cells which showed PCEs exceeding 10%.¹⁸⁵ Here, a layer of few hundred nm of CsPbI₃ NCs were sandwiched between TiO₂ and spiro-OMeTAD, which act as electron and hole selective contacts respectively, see Figure 137a,b.¹²⁸³ It was found that the CsPbI₃ NC-based solar cell devices showed improved operational stability as well as tolerance to higher relative humidity levels.

The high crystallinity of colloidal grown perovskite NCs reduces nonradiative recombination channels, reflected by an enhancement in the PLQY, especially if the surface states of NCs are properly passivated.^{1284,1285} This property is especially attractive for the development of photocatalytic systems,^{43,1286} optoelectronic devices¹⁰⁸⁹ and also for photovoltaic applications.⁵²³ The increase in PLQY to values higher than 80%, in conventional NCs, has been a process that has required a couple of decades of research.¹²⁸⁵ In contrast, immediately following the report of perovskite NCs⁶⁶ were reports with PLQY beyond 80%^{14,25} and soon after reports of NCs with PLQYs near-unity.⁵²⁰ Low nonradiative recombination is necessary for photovoltaic devices with high open circuit voltage, V_{oc} .¹²⁸⁷ Because of this, halide perovskite QD solar cells presents outstanding V_{oc} with several reports showing values greater than 1.25 V with up to 90% of the thermodynamically limited V_{oc} demonstrated.^{192,1288–1290}

While low nonradiative recombination ensures a high V_{oc} , achieving high efficiencies also require good transport properties of the photogenerated charges, along with an absorber layer thick enough to harvest all available incident light. A critical component fundamental for eliminating nonradiative recombination in colloidal NCs in general and of perovskite NCs in particular is the passivation of the NC surfaces with organic capping ligands. However, these organic ligands hinder charge transport. Therefore, a balance is

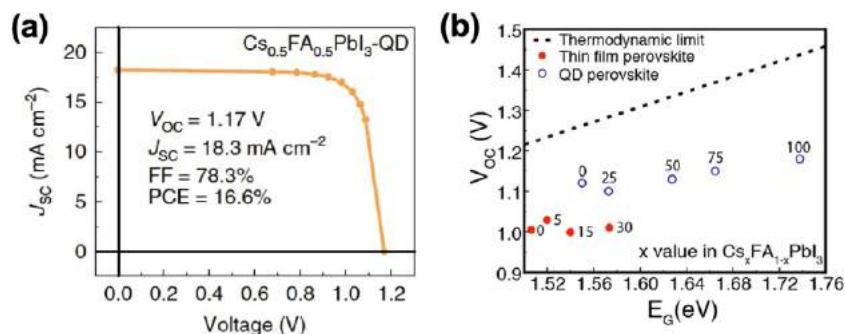


Figure 138. (a) Current–voltage characteristics of currently published world record QD solar cell; the device is based in $\text{Cs}_x\text{FA}_{1-x}\text{PbI}_3$ NCs. Reproduced with permission from ref 1269. Copyright 2020 The Authors under exclusive licence to Springer Nature Limited. (b) Comparison between V_{oc} obtained for perovskite QD solar cells, standard thin film solar cell, and the maximum thermodynamic limit. Reproduced from ref 1295. Copyright 2018 American Chemical Society.

required for proper passivation, such that the spacing between NCs is short, such that electron hopping can still occur. In Pb chalcogenide QD solar cells, transport properties are actively studied using a wide variety of ligand exchange strategies with many ligand head group options.^{1284,1291,1292} Perovskite NCs often have multiple ligand types (cationic and anionic species) which may be handled individually.^{1281,1282} Nevertheless, it is anticipated that with more work on designing better ligand motifs for halide NCs, as demonstrated for other NCs systems, perovskite QD solar cell performance may greatly increase.

FAPbI_3 is *a priori* more appealing for photovoltaic applications than CsPbI_3 due to a narrower band gap.¹²⁹³ However, due to transport limitations, the performance of perovskite QD solar cells based on FAPbI_3 NCs has not exceeded the efficiency of CsPbI_3 NCs. Nevertheless, the combination of CsPbI_3 with FAPbI_3 and/or $\text{Cs}_x\text{FA}_{1-x}\text{PbI}_3$ NCs in charge separating heterostructures (see Figure 137c,d) has enabled the PCE of perovskite QD solar cells to exceed 15%.^{1283,1294} Cells based on mixed cation NCs has also shown better performance than analogous devices but based on single cation NCs.^{192,1269} $\text{Cs}_x\text{FA}_{1-x}\text{Pb}(\text{I}_{1-x}\text{Br}_x)_3$ -based perovskite QD solar cells with band gaps larger than 1.8 eV exhibit V_{oc} values nearly 100 mV higher than those of the solar cells based on $\text{CsPb}(\text{I}_{1-x}\text{Br}_x)_3$ NCs.¹⁹² The currently published PCE record of QD solar cells of 16.6% was obtained with devices using $\text{Cs}_x\text{FA}_{1-x}\text{PbI}_3$ NCs as a light-harvesting material (see Figure 138a).¹²⁶⁹ In this achievement, the synthesis of the NCs with excess oleic acid ligand is reported to play a key role. In addition, it was demonstrated that the $\text{Cs}_x\text{FA}_{1-x}\text{PbI}_3$ NC-based solar cell devices exhibit significantly enhanced photo-stability compared with their thin-film counterparts, and they retain 94% of the original PCE under continuous solar illumination for 600 h.

Halide perovskite NCs may also be attractive for the development of multijunction solar cells as the wide gap component. However, there has not been a compelling demonstration published yet. First, the NCs offer band gap control by quantum-confinement effects in addition to composition. The versatility of halide perovskites allows the band gap to be easily tuned through the halide composition.^{765,1296} In bulk thin films, halide phase segregation is readily observed in mixed-halide perovskites under illumination^{1170,1297,1298} or when electrical bias is applied,¹²⁹⁹ limiting band gap stability in mixed perovskites. However, due to size constraints, phase segregation is suppressed in mixed-halide perovskites NCs in comparison with thin films.^{1172,1297,1300}

This may lead to more possibilities for achieving higher voltages in devices with band gap in the 1.8–2.0 eV range. Presently, perovskite QD solar cells often exhibit higher V_{oc} than bulk perovskites of similar band gap and composition, in the range of 1.55–177 eV (see Figure 138b).¹²⁹⁵ However, there are several key limitations of perovskite QD solar cells at this stage. One area is the development of greater versatility in terms of carrier selective contacts, such as being able to construct the cell in a p–i–n geometry instead of an n–i–p structure, or using contacts with lower thermal budgets for processing on other subcells. Another challenge is that increasing the band gap by quantum confinement or by introducing bromine has yet to produce a high efficiency solar cell with larger V_{oc} due to reductions in the lifetime. Likely a breakthrough in ligand exchange for improved passivation or more complex compositions that yield longer lifetimes and higher band gaps could be the key to realizing this potential in multijunction cells using high voltage perovskite NCs.

The fact that perovskite QD solar cells have now demonstrated >16% PCE is exciting in its own right; however, just having this distinct solar cell platform can enable us to learn more about metal-halide perovskites, in general. The high surface area to volume ratio enables studies of surface passivation, which could carry over to other areas in halide perovskite science. NCs can act as seeds for the nucleation of larger crystals. At this moment, it is not clearly known if both kinds of devices fully share the same working principles or if there are significant differences in effective carrier concentrations, junction characteristics, *etc.* Recent studies point to similar optoelectronic behavior as the impedance spectroscopy analysis highlights.¹³⁰¹ Furthermore, several groups have demonstrated improved characteristics in devices using heterojunctions containing a thin film layer and a QD layer.^{1279,1302,1303} For these reasons, perovskite QD solar cells offer us many more possibilities with high potential.

Lead-Free Perovskite NCs. As discussed in the **NANOCRYSTALS OF LEAD-FREE PEROVSKITE-INSPIRED MATERIALS** section, there has been extensive work in developing lead-free analogues to LHP NCs. Beyond lighting applications, these materials have also been investigated for photovoltaics. For example, tin-halide perovskite solar cells have achieved high photocurrents as it has a low band gap, high absorption coefficient and a symmetric perovskite crystal structure with disperse bands.^{1304,1305} The highest efficiency currently reported of bulk Sn-based perovskite solar cell is reported by Jokar *et al.*¹³⁰⁶ using a mixed cation (guanidinium

(GA^+), formamidinium (FA^+)), tin triiodide perovskite with ethylenediammonium diiodide (EDAI_2) as an additive. The PCE of the device is 9.6% with a J_{sc} of 21.2 mA cm^{-2} . Sn-based perovskite quantum dot solar cells have achieved comparable PCEs. For example, $\text{CH}_3\text{NH}_3\text{SnBr}_{3-x}\text{I}_x$ NC solar cells using mesoscopic TiO_2 anode has a PCE of 8.79%, V_{oc} of 0.758 V, J_{sc} of 17.06 mA cm^{-2} , and fill factor of 68.1%.¹³⁰⁷ Tin-based perovskite QRs have also been synthesized and investigated for photovoltaics. Chen *et al.* reported a CsSnX_3 QR solar cell with a PCE of 12.96% for CsSnI_3 . They also reported CsSnBr_3 and CsSnCl_3 QRs with 10.46% and 9.66% efficiency, respectively.⁵¹⁷ Similar work has also been reported by Chen *et al.* for CsGeX_3 QRs with a peak PCE of 4.92%.⁵³⁸ The bottleneck for tin-halide perovskite NC solar cells are low open circuit voltages. The average V_{OC} of Sn-based perovskite solar cells is around 0.5 V, which is significantly below their band gap of 1.2–1.4 eV^{1304,1308}. This is due to the facile and undesirable oxidation from Sn^{2+} to Sn^{4+} , which leads to p-type doping and an increase in the dark current density and photocarrier recombination.^{1308,1309} The PCEs of Sn-based perovskite solar cells are currently well below their Shockley–Queisser limit of 33%.¹³⁰⁸ Unlike lead-based perovskites, tin-based perovskites do not have inactive lone pair, which could provide oxidative resistivity. As a result, tin-based perovskites are extremely sensitive to oxidation induced self-doping, which leads to perovskite degradation. The future challenges include stabilizing the tin oxidation state to improve the defect-tolerant properties of Sn-based perovskite and solar cell performance. Apart from methods like partial substitution, additive engineering and addition of deoxidizer,¹²⁶⁸ developing low-dimensional structures, such as quantum dots, could be another approach to stabilize Sn-based perovskites, as NCs have less intrinsic defects caused by large surface to volume ratios and automatic elimination of volume defects.

Apart from isovalent substitution of lead, other lead-free perovskite NC solar cells have been investigated, including $\text{A}_2\text{B(I)B(III)X}_6$ double perovskite NCs, 0D $\text{A}_2\text{B(III)}_2\text{X}_9$, and 0D $\text{A}_2\text{B(IV)X}_6$ perovskite-inspired materials.^{95,352,1310} Cho *et al.*¹³¹¹ recently reported a $\text{Cs}_2\text{AgBiBr}_6$ double perovskite NC solar cell using semiconductor oxides such as TiO_2 or ZnO as the ETL. By depositing multiple layers (20 deposition cycles, 225 nm) of the QD film, the device achieved an open-circuit voltage of 0.92 V. Although this is similar to the V_{OC} of LHP solar cells, it is well below the ~ 2.1 eV band gap of $\text{Cs}_2\text{AgBiBr}_6$. Furthermore, the efficiency was only 0.13%. The low PCE cannot be further improved by simply increasing the thickness of the absorber layer as the material can only absorb light with wavelength below 550 nm due to the wide band gap.¹³¹² Also, the low fill factor (32%) indicated the QD films to have high series resistance.^{352,1311} Vacancy-ordered double perovskite $\text{A}_2\text{B(IV)X}_6$ is considered a 0D perovskite-inspired materials due to the absence of connectivity between BX_6 octahedra.³⁵² Many $\text{A}_2\text{B(IV)X}_6$ compounds have been investigated for potential photovoltaic applications, including MA_2SnI_6 ,¹³¹³ Cs_2TiBr_6 ,¹³¹⁴ (champion efficiency of 3.3%) and Cs_2PdBr_6 .¹³¹⁰ However, there are no reported quantum dots solar cell for these materials yet. Recently, Zhou *et al.* successfully synthesized Cs_2PdBr_6 NCs with single unit cell thickness and high stability.¹³¹⁰ The NCs demonstrated a measured photocurrent density of $1.2 \mu\text{A cm}^{-2}$ under an applied potential of $0.65 \text{ V}_{\text{Ag/AgCl}}$ with simulated solar light (AM1.5G, 150 mW/cm^2 , compared to lead-free perovskite thin-film NCs). It would be interesting to see if the

development of $\text{A}_2\text{B(IV)X}_6$ NC materials can further improve the performance of the solar cell, such as using 0D Cs_2TiBr_6 , as low-dimension quantum dots have larger surface to volume ratio and less volume defects. In general, comparing with lead-halide perovskite quantum dots solar cell, the research of lead-free perovskite NC solar cell is still at the beginning stage. There is a strong incentive to synthesis high-quality NC materials and fabricating more efficient lead-free quantum dots for solar cells applications, even though the current PCE of the cell remains low. The motivation would be it has been shown that NCs can stabilize thermodynamically unstable phase.¹³¹⁵ For example, the bulk perovskite cubic $\alpha\text{-CsPbI}_3$ black phase is unstable under room temperature, and the phase becomes metastable in the form of NCs and can survive for days in solution.¹⁸⁵

Conclusions and Outlook for MHP NC-Based Solar Cells. Currently, one of the main challenges for lead-free perovskite-inspired NCs is to achieve high efficiency and stability simultaneously. Sn-based NC solar cells have achieved the highest efficiencies among these materials, but the materials still suffer from instability issues. By contrast, stable materials such as bismuth-based (Bi) and antimony-based (Sb) double perovskites NCs, have low power conversion efficiency (less than 5%). The degradation mechanism has been discussed previously in the [Light-Emitting Devices](#) section. Although surface ligands are expected to stabilize the metastable phases of perovskites, the ligands are often removed either by washing or annealing for improving the charge transport across the films. Therefore, it is still unclear what density of ligands is required on the NC surface to promote phase stability. Currently, extensive studies have been made on improving the stability of solar cells made with perovskite bulk thin films.^{1316–1318} By following a similar logic, more works are required on quantum-dot-based solar cells, such as utilizing compositional engineering or using doped NCs. Furthermore, the candidates for solving the toxicity of lead-based perovskite should not be limited to perovskites materials; other perovskite-inspired materials such as chalcogenide NCs should also be explored, and these materials are detailed in reference.¹³¹⁹

Photocatalysis Using Perovskite NCs. Chemical fuels have significantly higher energy storage capacity than the batteries due to the very high specific energy of the former, which can be released by combustion.^{1320,1321} Harvesting the energy from chemical fuels through the use of solar radiation can enable the clean and efficient storage or renewable solar energy.¹³²² The common chemical fuels generated are hydrogen and oxygen (from water splitting), or methane (from CO_2 reduction).^{1323,1324} Photons in the UV and visible wavelength regions have sufficient energy to drive these photochemical reactions.¹³²⁵ Owing to their large specific surface area, NCs offer the possibility to both absorb solar radiation and drive the desired solar fuel generating reaction without any external bias.^{1326,1327} The attractive optical properties of halide perovskite NCs (for example, high absorption coefficients in the UV–visible region, a tunable band gap, and high PLQY) make them suitable candidates for solar-driven photocatalytic applications. While recent progress in the halide perovskite NCs leads to successful use in different optoelectronic filed, there use in the field of photocatalysis remains a challenge due to their instability in aqueous media.^{1328,1329} Here, we will provide the current development of perovskite NCs toward photocatalytic dye degradation, H_2

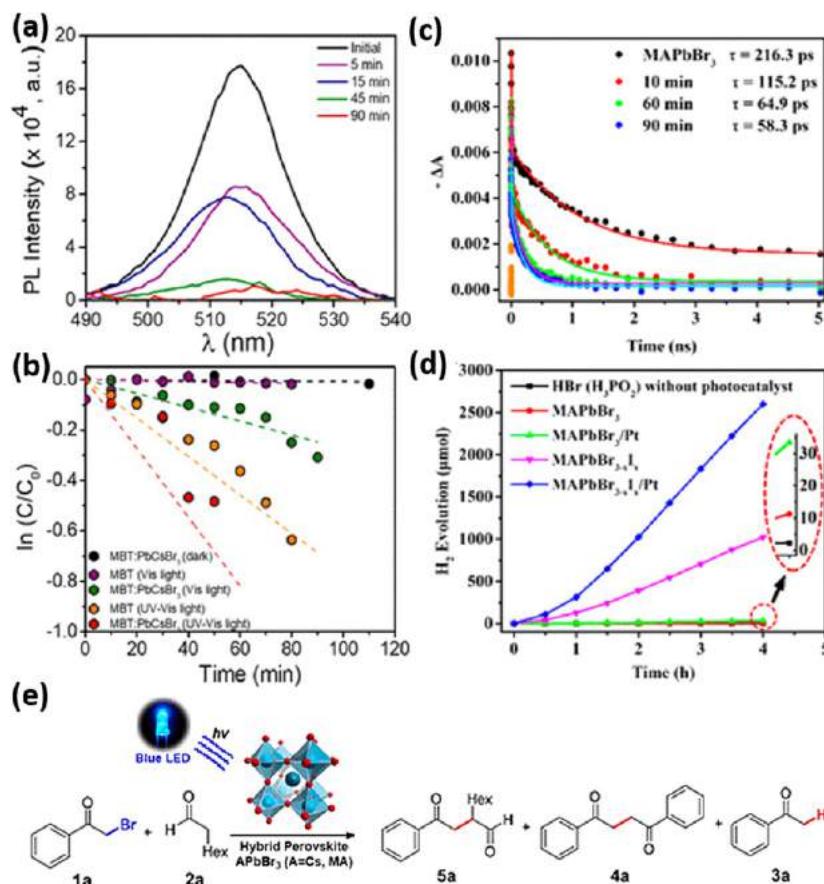


Figure 139. (a) PL spectra of CsPbBr₃ NCs in the absence and presence of 2-mercaptopbenzothiazole, under 100 mW cm⁻² irradiation with UV filter. (b) Relative change in MBT concentration (without and with CsPbBr₃) with time under visible and UV-visible light. (c) Bleach recovery kinetics of MAPbBr₃ (0 min) and MAPbBr_{3-xIx} at different time (10 to 90 min) of ion-exchange reaction as observed from transient absorption spectroscopy. (d) Photocatalytic activity of the H₂ evolution without and with different photocatalysts (MAPbBr₃, MAPbBr₃/Pt, MAPbBr_{3-xIx}, and MAPbBr_{3-xIx}/Pt). (e) APbBr₃ (A= Cs or MA) NCs for photocatalytic α-alkylation of aldehydes. Panels a and b are reproduced from ref 1286. Copyright 2019 American Chemical Society. Panels c and d are reproduced from ref 1330. Copyright 2018 American Chemical Society. Panel e is reproduced from ref 1331. Copyright 2019. American Chemical Society.

evolution as well as CO₂ reduction. First, we will discuss the photocatalytic activity of the Pb-based and Pb-free perovskite NCs, followed by photocatalytic activity of halide perovskite-based heterostructures.

Photocatalysis with Pb-Based Perovskites. Most of the developed waste water treatment strategies primarily separate only organic contaminants from water. However, it is necessary to convert these contaminants to nontoxic substances. The outstanding optoelectronic properties of lead-halide perovskites, *e.g.*, CsPbBr₃ NCs can be used for the photocatalytic degradation of organic pollutants and convert them to nontoxic substances. The photocatalytic degradation of a common organic pollutant 2-mercaptopbenzothiazole (MBT) in the presence of CsPbBr₃ NCs has been investigated systematically.¹²⁸⁶ MBT is a poorly biodegradable heterocyclic organic compound which causes severe toxicity in the aqueous solution. As has been shown in Figure 139a, the PL intensity of CsPbBr₃ NCs reduces drastically in the presence of MBT. The energy level alignment between CsPbBr₃ NCs and MBT suggests a photoinduced hole transfer from the perovskite NCs to MBT, which results in PL quenching. This leads to the oxidation of MBT in the presence of lead-halide perovskite NCs and results complete degradation of the pollutants. Time-resolved PL measurements further support the hole-transfer phenomenon.¹²⁸⁶ To unambiguously determine the role of

lead-halide perovskite NCs in MBT photodegradation, several control experiments were carried out and shown as relative concentration of the contaminant with time in Figure 139b. It is evident from the experiments that in the absence of the perovskite NCs, only UV light is effective for the degradation of MBT. However, in the presence of the CsPbBr₃ NCs, significantly faster photodegradation of MBT takes place under both visible and UV irradiation. The photodegradation rate constant for MBT has been calculated from the linear plot of ln(C/C₀) versus *t*, assuming a pseudo-first-order reaction (Figure 139b). The calculated rate constant suggests, although in the presence of UV irradiation, the photodegradation rate of MBT doubled with CsPbBr₃ NCs; however, in the presence of visible irradiation, the rate becomes 6-fold faster with CsPbBr₃ NCs. The zero response toward photodegradation of MBT in the presence of CsPbBr₃ NCs in the dark eliminates the possibility of any competing mechanism.

Employing a light-assisted halide exchange method in aqueous HBr/HI solution, mixed-halide MAPbBr_{3-xIx} perovskite has been synthesized from pristine MAPbBr₃, which processes a band gap–funnel structure.¹³³⁰ Such a structure results in an iodine concentration gradient within the perovskite, where the iodine concentration increases gradually from the core to the surface of the NC. This enhances the charge transport properties toward the surface, which is

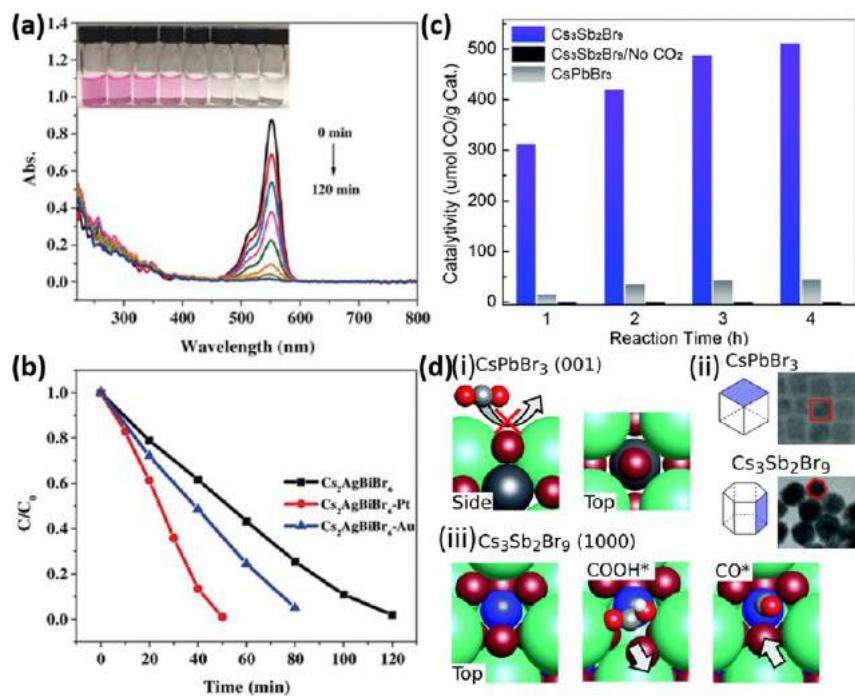


Figure 140. (a) UV-vis absorption spectra of Rhodamine-B in the presence of $\text{Cs}_2\text{AgBiBr}_6$ at different irradiation times (between 0 and 120 min). Inset: Digital photographs of the corresponding photocatalyst at different irradiation times. (b) C/C_0 plot as a function of irradiation time for photodegradation of RhB in the presence of $\text{Cs}_2\text{AgBiBr}_6$, $\text{Cs}_2\text{AgBiBr}_6$ -Pt, and $\text{Cs}_2\text{AgBiBr}_6$ -Au. Reproduced with permission from ref 1333. Copyright 2019 John Wiley & Sons, Inc. (c) Photocatalytic activity toward production of CO by $\text{Cs}_3\text{Sb}_2\text{Br}_9$ NCs compared to CsPbBr_3 NCs. (d) (i) Inaccessible Pb atoms as shown on the CsPbBr_3 (001) surface. (ii) TEM image showing cubic CsPbBr_3 and hexagonal $\text{Cs}_3\text{Sb}_2\text{Br}_9$ NCs, along with the planes of (001) for CsPbBr_3 and (1000) for $\text{Cs}_3\text{Sb}_2\text{Br}_9$. (iii) Reactivity of highly exposed $\text{Cs}_3\text{Sb}_2\text{Br}_9$ NCs (1000) surface *via* partial displacement of one of the Br atoms. Reproduced with permission from ref 1335. Copyright 2020 Royal Society of Chemistry.

beneficial for photocatalytic reactions at the surface of the perovskites. The photogenerated electron–holes thus can migrate toward the surface through such band gap-funneled perovskite and can initiate the photocatalytic reaction. To understand the charge carrier dynamics induced by the halide-exchange reaction, ultrafast transient absorption spectroscopy has been performed. The TA spectrum of pristine MAPbBr_3 shows a ground-state bleach at 526 nm due to photoinduced phase-space filling from electrons and holes.¹³³⁰ However, the 90 min iodine exchange perovskite sample shows only a 10 nm red shift in the bleach signal, suggesting the TA spectrum is dominated by Br ions in the $\text{MAPbBr}_{3-x}\text{I}_x$. In other words, the bromide ions inside the particle are only partially replaced by the iodide ions which supports the band gap–funnel structure. However, comparing the ground-state bleach recovery kinetics of MAPbBr_3 and $\text{MAPbBr}_{3-x}\text{I}_x$ at different time of the ion-exchange reaction (Figure 139c) reveals significantly faster bleach recovery signal for longer time iodide exchange perovskites. This indicates on increasing iodine content at the surface (at longer time ion-exchange reaction), charge transport toward surface increases significantly due to the band gap–funnel effect, which results in faster recovery of the bromide-rich photobleach signal. To corroborate the enhanced charge transport property toward better photocatalytic performance in the band gap-funnel $\text{MAPbBr}_{3-x}\text{I}_x$ perovskite, photocatalytic H_2 evolution reaction has been performed under visible-light irradiation. The pristine MAPbBr_3 shows poor photocatalytic H_2 evolution performance (2.8 mmol/h) which improves to 8.4 mmol/h after loading on Pt (Figure 139d). Surprisingly, after introducing the band gap-funneled

$\text{MAPbBr}_{3-x}\text{I}_x$ perovskite, the activity increases significantly to 255.3 mmol/h. Expectedly, on loading with Pt, a further 2.5-fold (651.2 mmol/h) enhancement was observed as a result of efficient separation of the photogenerated electron–hole.

Zhu *et al.* demonstrated the C–C bond coupling organic reactions using APbBr_3 ($\text{A} = \text{Cs}$ or MA) as photocatalysts.¹³³¹ As shown in Figure 139e, under visible-light ($\lambda = 450$ nm) irradiation, APbBr_3 NCs can selectively produce several products, including dehalogenated acetophenone **3a** (yield 76%), sp^3 C coupling product **4a** (8%), and α -alkylation product **5a** (7%). In addition, the broad reaction scope of this important organic transformation, especially the tolerance of sophisticated biorelevant functional groups, indicates the feasibility of employing halide perovskites for photo-driven pharmaceutical molecule synthesis. In another work,¹³³² they further demonstrated the halide perovskites NCs can catalyze a series of organic reactions, such as C–C bond formations *via* C–H activation, C–N bond formations *via* N-heterocyclizations and C–O bond formations *via* aryl esterifications. In this work, the impacts of reaction conditions (e.g., the size of NCs, solvent types, acid/base, and air tolerance, *etc.*) on the performance of CsPbX_3 ($\text{X} = \text{Cl, Br, I}$) NCs were systematically investigated, which provide important guidance for expanding the application of halide perovskite-driven organic reactions. Another interesting example of the use of perovskites in photocatalysis is that of CsPbBr_3 nanoparticles as photosensitizers for a demanding photoredox catalytic homo- and cross-coupling of alkyl bromides at room temperature by merely using visible light and an electron donor, as demonstrated by Pérez-Prieto and co-workers.³⁴⁸

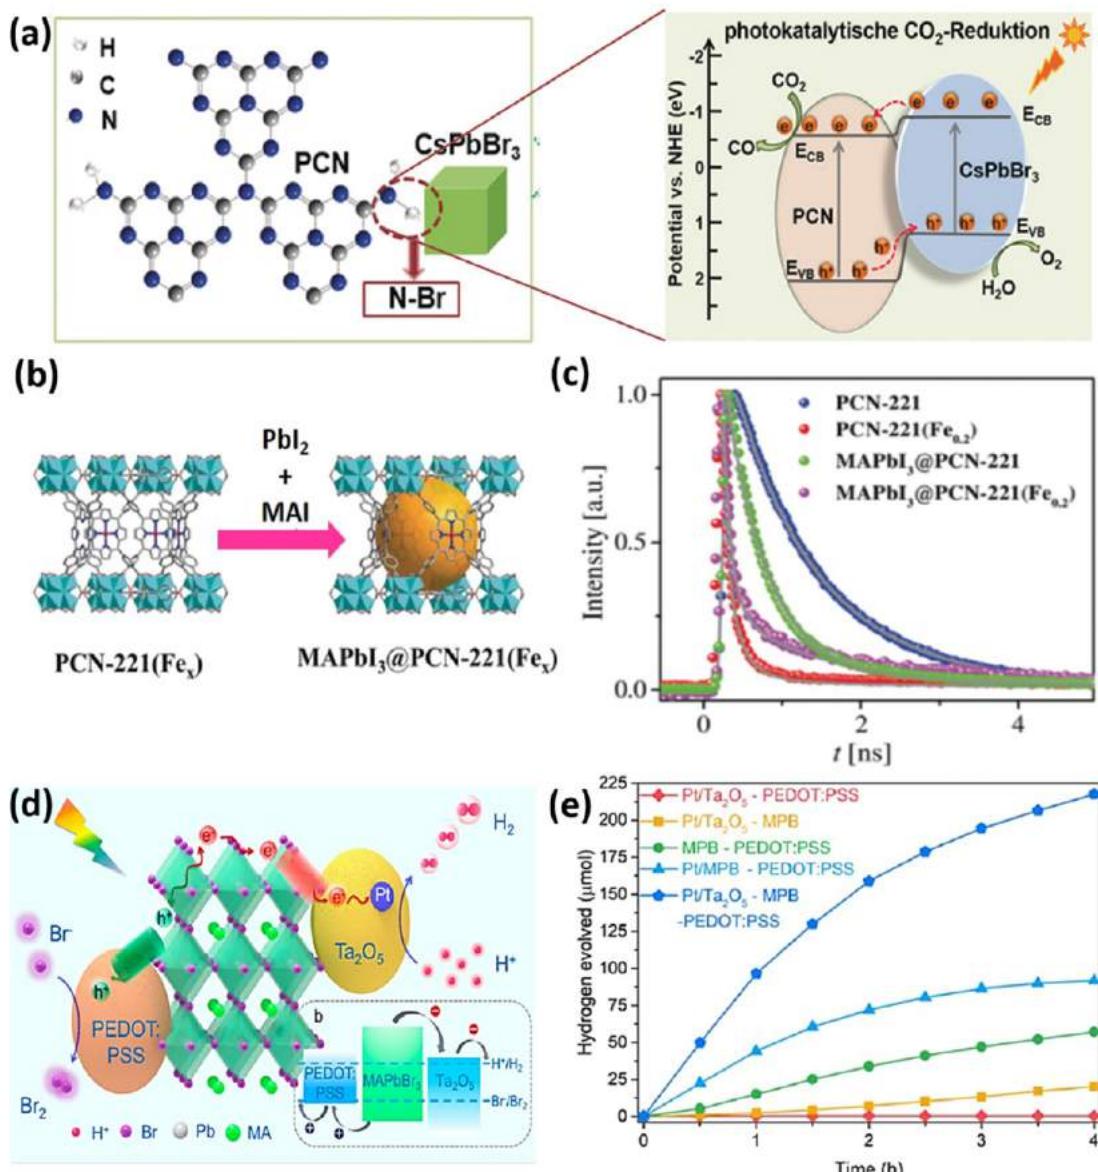


Figure 141. (a) Schematic illustrations for the interfacial interaction and band alignment within CsPbBr_3 NCs/g- C_3N_4 heterojunction. Reproduced with permission from ref 1337. Copyright 2018 John Wiley and Sons. (b) Schematic illustration for the synthesis of MAPbI_3 @PCN-221(Fe_x). (c) TRPL decays of different samples. Reproduced with permission from ref 1338. Copyright 2018 John Wiley & Sons, Inc. (d) Schematic illustration of the mechanism of photocatalytic HER over $\text{Pt}/\text{Ta}_2\text{O}_5$ -MAPbBr₃-PEDOT:PSS heterojunction. (e) Comparison of the H_2 evolution activities of $\text{Pt}/\text{Ta}_2\text{O}_5$ -PEDOT:PSS, $\text{Pt}/\text{Ta}_2\text{O}_5$ -MAPbBr₃, $\text{Pt}/\text{MAPbBr}_3$ -PEDOT:PSS, MAPbBr₃-PEDOT:PSS, and $\text{Pt}/\text{Ta}_2\text{O}_5$ -MAPbBr₃-PEDOT:PSS. Reproduced from ref 1340. Copyright 2018 American Chemical Society.

The building of a high concentration of the generated radical anions in the NC surface eventually facilitated the exergonic C–C bond formation, thus demonstrating the cooperative action between the nanoparticle surface and the organic capping.

Photocatalysis Using Pb-Free Perovskites. While lead-halide perovskites demonstrate significant potential toward different optoelectronic properties including photocatalysis, the toxic nature of Pb limits its large-scale application. Furthermore, metal centers (e.g., Bi, Sb) other than Pb may allow higher activity and better selectivity toward photocatalysis. An alcohol-based Pb-free $\text{Cs}_2\text{AgBiBr}_6$ double perovskite has been developed recently which shows a great promise toward dye degradation under visible-light irradiation with high chemical stability.¹³³³ $\text{Cs}_2\text{AgBiBr}_6$ has been studied for

photocatalytic degradation of Rhodamine-B (RhB), a common organic contaminant, under visible-light irradiation (Figure 140a), which shows up to 98% degradation of the dye upon a continuous irradiation for 120 min. The photocatalytic activity of $\text{Cs}_2\text{AgBiBr}_6$ was enhanced after depositing Au and Pt on the surface (Figure 140b), which improves the charge transport efficiency and has been verified using steady-state and time-resolved PL quenching measurements.

Although the photocatalytic activity of lead-free double perovskites is promising, the stability of this material remains challenging. In this respect, lead-free $\text{Cs}_3\text{Sb}_2\text{X}_9$ and $\text{Cs}_3\text{Bi}_2\text{X}_9$ defect-ordered perovskites are promising and have greater thermal stability.^{544,1334} The photocatalytic activity of $\text{Cs}_3\text{Sb}_2\text{Br}_9$ perovskite for CO_2 reduction reaction has been explored recently.¹³³⁵ Unlike the commonly used solvent ethyl

acetate or acetonitrile, in this work high boiling-point octadecene was chosen due to its larger CO_2 solubility. Figure 140c compares the photocatalytic activity toward CO_2 reduction of $\text{Cs}_3\text{Sb}_2\text{Br}_9$ and CsPbBr_3 perovskite NCs. Over the course of 4 h irradiation, CsPbBr_3 NCs produces 50 mmol/g CO, which is higher than that in previous reports. This has been attributed to increased CO_2 solubility as well as reduced degradation of perovskite NCs in octadecene compared to that with commonly used acetonitrile or ethyl acetate for photocatalytic reactions. Surprisingly, the activity of $\text{Cs}_3\text{Sb}_2\text{Br}_9$ NCs to CO_2 reduction is more than 10-fold higher, producing a total of 510 mmol/g CO after 4 h irradiation (Figure 140c). The control experiments in the absence of CO_2 shows no CO production which confirms the result of CO generation is not from the degradation of ligands or solvent. The activity of both the catalysts was found to be reduced over the multiple reaction cycles. However, the $\text{Cs}_3\text{Sb}_2\text{Br}_9$ NCs still showed a 5–10-fold larger activity than Pb-based CsPbBr_3 NCs. Density functional theory calculations were performed to unravel the underlying cause for such enhanced activity in $\text{Cs}_3\text{Sb}_2\text{Br}_9$ NCs.¹³³⁵ No intermediate COOH^* -bound states were observed on the CsPbBr_3 NC (001) surface from the calculations. This is because the Pb atom is completely isolated from the surface by the Cs and Br atoms, as shown in Figure 140d(i), which restricts any direct interaction with COOH^* . The (1000) and (0001) surfaces of $\text{Cs}_3\text{Sb}_2\text{Br}_9$ NCs, however, have high exposure due to the hexagonal structure (Figure 140d(ii)). Here, the Sb atom is only partially shielded by three Br atoms (Figure 140d(iii)). An Sb–C bound state is observed in the DFT calculation for both (1000) and (0001) surfaces for COOH^* , where one of the ionic Br ions displaces slightly to allow the formation of the Sb– COOH^* bond. The smaller size of CO^* allows the shifted Br to return to its initial position during the evolution of CO. Thus, DFT calculations show that the mechanism for the enhanced photocatalytic activity of $\text{Cs}_3\text{Sb}_2\text{Br}_9$ NCs is due to the effective binding sites on the (1000) and (0001) surfaces for COOH^* and CO^* intermediates.

Photocatalytic Activity of Perovskite-Based Heterostructures. The high absorption coefficient, defect-tolerance and tunable band positions of halide perovskites are strongly beneficial for photocatalysis. In addition to efficient charge separation and transfer, photocatalysts also require a high density of active sites, good stability and recyclability. Generally, it is difficult to satisfy all these requirements for a single-component halide perovskite photocatalyst. Owing to the synergistic properties induced by the interactions among different components, heterostructures of diverse functional materials into a single system with precise design is a commonly employed strategy to enhance the performance of semiconductors.¹³³⁶ Halide perovskite-based heterostructures have therefore demonstrated improved performance. For instance, based on a facile self-assembly method, Ou *et al.*¹³³⁷ prepared CsPbBr_3 NCs anchored on porous g-C₃N₄ nanosheet heterojunctions for CO_2 photoreduction. The intimate interface interaction enable by N–Br chemical bonding as well as the matched band alignment between CsPbBr_3 and g-C₃N₄ semiconductors effectively facilitate the separation and transport of photogenerated carriers (Figure 141a). As a result, the optimal CsPbBr_3 /g-C₃N₄ heterojunction exhibits enhanced stability and CO production compared to CsPbBr_3 NCs and g-C₃N₄ alone.

Metal-organic frameworks are also promising CO_2 catalysts due to their porous crystalline framework offering a large specific surface area and highly active metal centers for selective CO_2 absorption/activation. Recently, Wu *et al.*¹³³⁸ prepared Fe-based MOF-coated MAPbI₃ perovskites (*i.e.*, MAPbI₃@PCN-221(Fe_x)) *via* a sequential deposition method (Figure 141b). TRPL measurements in Figure 141c suggest that the electron transfer from MAPbI₃ to Fe-based MOFs reaction sites greatly promotes efficient charge separation. The MAPbI₃@PCN-221(Fe_x) can serve as efficient photocatalysts for CO_2 reduction with the highest yield of 19.5 $\mu\text{mol g}^{-1} \text{h}^{-1}$ for solar fuel production ($\text{CH}_4 + \text{CO}$). In addition to MOFs, other porous materials such as silica matrixes,¹³³⁹ TiO₂¹²⁹³, and graphene³⁸ have also been employed as support to stabilize and disperse halide perovskite, thus tuning their photocatalytic performance.

As shown in Figure 141d, a multicomponent halide perovskite-based hybrid consisting of MAPbBr₃ modified with Pt/Ta₂O₅ as electron transport layers and poly(3,4-ethylenedioxythiophene):polystyrenesulfonate as hole transport layers were reported by Wang *et al.*¹³⁴⁰ The photocatalytic H₂ evolution rate of this catalyst reached 105 $\mu\text{mol h}^{-1}$, which was drastically increased about 52-fold over the pristine MAPbBr₃ (Figure 141e). However, the photoactivity of this system decreased gradually with prolonged reaction times, indicating poor stability of the reaction. Sá and co-workers developed a photocatalytic reaction system that employed CsPbBr_3 as the light-absorber and Ru@TiO₂ nanoparticles as the proton reductant catalyst.¹³⁴¹ Stable H₂ production was observed, which suggest that this reaction system can be a feasible platform for fundamental investigations on halide perovskites photoactivity and stability.

Summary and Outlook for Perovskite Photocatalysis.

Inspired by these pioneering works, various halide perovskite materials with tunable size, morphology and crystal structure have been prepared by a range of methods. These halide perovskites can also be incorporated with metal nanostructures,¹³¹⁵ semiconductors¹³⁴² and carbon-based materials^{1343,1344} to form heterojunction photocatalysts. Recent advances of halide perovskite in photocatalysis fields show that these materials can be used to drive H₂ evolution, CO_2 reduction, degradation of organic pollutants, and selective organic synthesis. Thus, it may be concluded that the renaissance of halide perovskites in the photovoltaic and optoelectronic fields has also sparked considerable interest in their photocatalytic applications. Currently, the highest CO_2 to solar fuel (CO + CH₄) production rate has reached 431 $\mu\text{mol g}^{-1} \text{h}^{-1}$ with transition metal Ni complex modified CsPbBr_3 ,¹³⁴⁵ and the maximum H₂ generation rate of 7.3 mmol $\text{g}^{-1} \text{h}^{-1}$ was gained with BP/MAPbI₃ heterojunctions.¹³⁴² Despite the exciting progress, the field is still at its infancy and there is great room for the design of target reaction systems, enhancing the stability and efficiency and eliminating toxicity of the halide systems for solar to chemical energy conversion.

The future development of halide perovskite-based photocatalysts can be divided into the following aspects:

1. The reaction type and scope of metal-halide perovskites can be expanded by fine-tuning the structural composition which may lead to efficient manipulation of the band gap and alignment. For example, doping Sn in the B-site of MAPbI₃ lead to reduction in the band gap which may lead to enhanced light absorption. Such engineering may lead to the develop-

ment of different types of photocatalysts with improved charge-transfer efficiency.

2. The photocatalytic performance of metal-halide perovskites can be improved by structural engineering toward stability, reactivity and selectivity, *e.g.*, by ligand engineering, doping, surface modification with cocatalysts, surface passivation layers. This may result in increasing stability as well as enhanced reactivity and boost in the photocatalytic performance. For example, the stability can be enhanced using bulky organic ligands (*e.g.*, butylamine) which may reduce the dimension of 3D perovskite to 2D perovskite. The diffusion length can be enhanced in MAPbI_3 by A-site (X-site) doping of MA (I) with FA (Br) and suppress electron–hole recombination, leads to increased reactivity. For selective charge-extraction, several electron and hole transporting materials (*e.g.*, GO, MOF, *etc.*) can be used in combination with the perovskite, as discussed above.

3. Furthermore, development of efficient eco-friendly Pb-free metal-halide perovskites by replacing Pb with other transition metals (*e.g.*, Sn, Sb, Bi, Ag, *etc.*) is necessary, though the Pb-free perovskites suffer from reduced activity. Thus, development of such Pb-free photocatalysts should occur in combination with several improving strategies.

OVERALL SUMMARY AND OUTLOOK

Over the last few years, perovskite NCs have quickly emerged as an important class of semiconductors. Research into perovskite NCs has been sparked not only because of their intriguing fundamental optical and electronic properties, but also by their appeal in many semiconductor-based technologies. This review has covered most of the lines of research that are being carried on perovskite NCs. Most of these lines of research only started a few years ago, and range from synthesis to self-assembly and characterization, through to applications. Tremendous research progress has been made in these various research areas in a short span of time, yet there are many open questions and challenges to be addressed to move the field forward.

Shape/Composition-Controlled Synthesis and Self-Assembly of MHP NCs. A wide range of synthetic methods have been developed for the preparation of perovskite NCs on a large scale using different precursors and ligands. Various morphologies include nanocubes, NPLs, NWs, and NRs. The size and shape of the perovskite NCs is usually controllable by the reaction temperature, the ratio of acid–base ligands, precursor ratio (A to B), the alkyl chain length of the ligands, and the thermodynamic equilibrium of the reaction.^{18,47,60,145,150} However, the level of shape control in MHP NCs is far from what has been achieved for metal nanoparticles and classical colloidal quantum dots. Most of the synthesis methods reported for MHP NCs generally yield nanocubes or cuboid morphologies.^{36,52} The crystallization of perovskite NCs is an extremely fast process, which makes it difficult to probe their growth mechanisms. Therefore, it is still challenging to understand the nucleation and growth processes of perovskite NCs for a precise control of their morphology. An approach that could be used to slow-down the reaction speed is using precursors that react at a lower rate. In general, fast nucleation and growth result in isotropic NCs, while slow growth processes lead to anisotropic colloidal NCs. This is indeed the case for metal NPs. However, in the case of perovskite NCs, it is still unclear how 2D NPLs are formed from an isotropic crystal lattice and homogeneous reaction

environment. It is most likely that the symmetry breaks as soon as nucleation occurs and the NCs grow into 2D shapes rather than 3D. Another possibility is that the ligands could bind to specific facets of the nucleus more strongly than others and restrict growth, resulting in growth being anisotropic. To prove these speculations, in-depth studies on growth mechanisms are needed. On the other hand, it has been revealed that the formation of perovskite NWs occurs through the oriented-attachment of nanocubes rather than a seed-mediated growth process.^{22,186,233,1346} Although this is well-understood for thick (10–12 nm thickness) nanowires, the growth mechanism of ultrathin (2–3 nm) NWs is still unclear. Despite decent progress in inorganic perovskite NWs, controlling their length scales is still challenging. One possible way to better control the shape of perovskite NCs is to further elaborate on the use of preformed, sub-nanometer perovskite clusters, as those developed by Peng *et al.* and employed for the synthesis of perovskite NCs of different shapes.³¹⁶ These clusters are expected to be less reactive than the direct metal and halide precursors and are already capped by ligands, providing at the same time all what is needed for the synthesis of NCs and preventing a massive nucleation of NCs.

Also, the level of control over the shape and polydispersity achieved in inorganic perovskite NCs has not been realized in OIHP NCs. In fact, researchers have paid more attention toward inorganic perovskite NCs due to their higher stability and shape purity compared to OIHP NCs. Despite the poor stability caused by the organic component, thin films of OIHPs have been shown to be potential candidates for photovoltaics. Therefore, it would be interesting to pay more attention to OIHP NCs in the future and compare their properties with inorganic perovskite NC.

One of the most interesting properties of perovskite NCs is their tunable PL by the constituted halide composition. Halide ion exchange in perovskites is relatively easy and it takes place at room temperature due to spontaneous halide ion migration, and has been applied to LHP NCs of different morphologies to tune their emission color. However, spontaneous halide exchange is a problem for the fabrication of white LEDs based on all-perovskite NCs. A few reports demonstrate the prevention of halide exchange between perovskite NCs of different halide components, but then the surface coatings used for preventing halide exchange can be a problematic for charge carrier transport. Therefore, this issue needs further attention in the future. In addition, cation exchange reactions have also been applied to obtain mixed cation perovskite NCs with distinct optical properties as compared to either all-inorganic or OIHP NCs. However, this has been mostly applied to nanocubes. It would be important to determine if anisotropic NCs such as NPLs, NWs and NRs retain their shape after cation exchange. More importantly, the mechanism of cation exchange is not yet well-understood. There is still an open question regarding whether the addition of cations can lead to re-nucleation or to an actual, topotactic replacement of the original cations of the crystal lattice. There is also a considerable work to be done on the transformations involving cesium-halide NCs and their interconversions.¹³⁴⁷ In this list, we consider CsX , Cs_4PbX_6 , the perovskite phase of CsPbX_3 , and CsPb_2Br_5 . It has been recently shown by Toso *et al.*¹³⁴⁷ that there is a common thread linking all these materials, that is, the Cs^+ cation substructure: this substructure is expanded/contracted and/or twisted when one material of this class converts into another material of the same class, but it is not

destroyed. This helps to rationalize the observation of heptaxial interfaces (some in NCs, other in bulk films), for example, $\text{CsBr}/\text{CsPbBr}_3$, $\text{Cs}_4\text{PbBr}_6/\text{CsPbBr}_3$, and $\text{CsPbBr}_3/\text{CsPb}_2\text{Br}_5$, in which there is a continuity of the Cs^+ substructure across the interface. This mechanism of preservation of the large “A” cation might be more general and expandable to a broad series of metal halides, and it would be interesting to the study other possible transformations in perovskite and perovskite-related materials.

The soft and highly dynamic nature of the perovskite crystal lattice results in liquid-like properties. This property makes the aggregated perovskite NCs perfectly single-crystalline. For instance, it has been shown that CsPbBr_3 nanocubes and NPIs can transform into single-crystalline NWs and nanobelts, respectively.^{22,234} Similarly, it has been often observed that the nanocubes on TEM grids connect with their neighboring nanocubes either side-by-side or corner-to-corner.³¹⁹ Very interestingly, most connected NCs appear to be single-crystalline, suggesting the liquid crystalline behavior of the lattice. However, it is still unclear how the lattice restructures at the connected joints. Further investigation will be required through high-resolution electron microscopy into what happens at the connected joints of the NCs.²²

Surface Chemistry and Surface Passivation/Coating of MHP NCs. There has been significant progress in the understanding of the surface chemistry of perovskite NCs through NMR studies, which were aimed to explore how the ligands could bind and stabilize the NC surface. It has often been stated that the ligands control the growth process, but we have only limited knowledge of how the ligands control the nucleation and growth of perovskite NCs. The studies suggest that bidentate and tridentate ligands are more suited to stabilizing the NC surface compared to the routinely used OLA/OA system. However, the chemistry behind ligand coordination to the NC surface remains unclear. It has been stated that the ligands are weakly bound to the surface of perovskite NCs and that this binding is highly dynamic due to the ionic character of such binding. The ligands are easy to detach from the NC surface during washing with polar solvents, and this creates surface defects, which affects their PLQY. A large number of studies have been focused on surface passivation of LHP NCs using various ligand molecules and metal halides to recover their PLQY. However, we know very little about the surface passivation mechanism at the atomic level. It is still unclear whether the ligand molecules alone can passivate the surface or if metal halides are compulsory to fill Pb and halide vacancies. More importantly, it is worth mentioning that there are differences in the trap energies and the interactions of ligands with perovskites of different halide compositions. Therefore, we cannot generalize the surface passivation mechanism for all halides. Until now, most reported studies into surface passivation have focused on the CsPbBr_3 NC system to improve their PLQY to near-unity.

One of the important problems associated with perovskite NCs is their instability in water. To address this issue, LHP NCs have been coated with various shell materials such as bulky organic ligands, TiO_2 , SiO_2 , Al_2O_3 , and block copolymers. However, these shells affect charge transport in corresponding optoelectronic devices. Therefore, more research efforts are needed to find conductive shells for perovskite NCs to improve their stability in water, but without affecting charge transport.

Future Prospects of 0D Non-perovskite NCs. We have summarized the recent developments in the synthesis, phase transformation, and optical features of Cs_4PbBr_6 NCs, particularly focusing on the material’s molecular behavior, the origin of green emission, and optoelectronic applications. However, there are still many challenges and possibilities lie ahead for exploring these class of materials in optoelectronics. Here, we share a few future prospects for the advancement of fundamental understanding of Cs_4PbBr_6 NCs as well as the development of additional 0D NCs, which would facilitate their applications.

1. Although different synthesis methods have been developed for Cs_4PbX_6 NCs, other 0D A_4PbX_6 NCs, such as Rb_4PbBr_6 , have not yet been reported. Thus, there is a large scope for the development of synthesis methods that allow precise control over the size and phase of 0D NCs with different A-site cations, and for uncovering the relationship between A-site cations and the optical properties of A_4PbX_6 NCs.

2. The origin of green emission in Cs_4PbBr_6 NCs is still under debate. It is attributed to the presence of 3D CsPbBr_3 impurities as well as defect-related emission. Therefore, sophisticated synthesis and characterization methods are needed to identify their emissive centers. For example, to confirm the role of defect-induced emission, low-dose HRTEM and data processing methods can be used to image the point defects in Cs_4PbBr_6 nanoplates of thickness less than 2 nm.

3. Developing lead-free 0D NCs for optoelectronic applications is another important research direction regarding this class of materials. For instance, Cs_4SnBr_6 NCs were recently synthesized, and they exhibit the characteristic green emission with enhanced air stability in the form of both colloidal suspensions and thin films.⁸⁰⁰ Furthermore, it was demonstrated that the lead-free $\text{Cu}(\text{I})$ -based 0D NCs (*i.e.*, $\text{Cs}_3\text{Cu}_2\text{X}_5$) display efficient luminescence and improved stability compared to that of Pb-based 0D NCs.^{558,1348}

4. Like Pb-free perovskite NCs, stability is also a major concern for Pb-free 0D NCs. To address the issue related to oxidation of Sn(II)- and Cu(I)-based 0D NCs, core/shell strategy can be used. Theoretical studies have predicted that $\text{A}_4\text{SnX}_6/\text{A}_4\text{PbX}_6$ core/shell-type NCs exhibit type-I energy level alignment for promoting the energy transfer from shell to the core and thus boosting the emission of A_4SnX_6 core.¹³⁴⁹ However, additional innovations in synthesis methods are required to realize 0D core/shell NCs.

Outstanding Questions into the Doping of MHP NCs.

Recently, there has been an explosion of research into the doping of perovskites with various metal ions, with the aim of improving stability, improving PLQY, and tuning the emission wavelength. Despite great progress into the doping of perovskite NCs, there are still a number of transition and inner transition metals that remain unexplored. With different dopants, additional optical and magnetic properties may be achieved. While B-site doping is largely explored, there should be more focus on A-site doping and on the influence on the stability and properties of the NCs. One of the important and open questions in the doping of perovskites is the exact location of the dopant sites in perovskite NCs. In most studies, it has been speculated that the dopants occupy the A-site or B-site regardless of their sizes. However, one should know that if the size of the dopant ion is too different from that of the cations of the host matrix, there may be phase segregation or the dopants destabilize the perovskite crystal structure. It is still

remains unexplored whether the dopants are substitutional in the crystal lattice or they simply stay on the surface of the crystal lattice.

Pb-Free Perovskite NCs. Beyond lead-containing perovskite NCs, a wide range of lead-free alternatives have been explored. These are termed perovskite-inspired materials (PIMs) because the main motivation is to find materials that could replicate the exceptional optoelectronic properties of the lead-halide perovskites. PIMs include halide perovskites based on Sn and Ge (ABX_3), Cu-based materials, Sb- and Bi-based vacancy-ordered perovskites ($A_3B_2X_9$), double perovskites ($A_2B(I)B(III)X_6$), and vacancy-ordered double perovskites ($A_2B(IV)X_6$). The synthesis routes are similar to those for lead-halide perovskites. Although the performances (such as PLQY, narrowness of the PL line width) of these materials have not matched the lead-based perovskites, they have given rise to distinctive applications. These include blue phosphors (namely, with $A_3B_2X_9$ compounds), which lead to white-light emission when combined with conventional yellow phosphors. Other materials (namely, double perovskites) have demonstrated promise as white-light phosphors. This emission is attributed to self-trapped excitons. The key advantage of these phosphors is that the materials demonstrate improved ambient and thermal stability over lead-halide perovskites. However, it is currently rare to find examples of lead-free NCs used in electrically driven applications. Promising results have so far been obtained from $Cs_3Cu_2I_5$ and $Cs_3Sb_2Br_9$ NC LEDs, and there has also been the demonstrations of direct injection into self-trapped excitons in tin-based perovskites. Further work on improving the properties of lead-free NCs and developing these materials for electrically driven applications is still needed.

Morphological and Structural Characterization. The characterization of perovskite NCs by TEM and X-ray scattering techniques is important for understanding their structure-property relationships. Perovskites are highly sensitive to the high-energy electron beam, which can lead to structural damage or phase transitions. NCs are particularly susceptible because Pb degradation products preferentially form at edges and corners. In particular, OIHP NCs are very difficult to characterize by high-resolution TEM because of the rapid degradation of the organic component. Using instruments with higher sensitivity has enabled reduced dosing of perovskites during characterization. As an example, this made it possible for $MAPbBr_3$ NCs to be measured with atomic resolution by TEM. However, unlike metal NPs, electron microscopy has not been utilized with its full potential in the characterization of perovskite NCs due to its beam sensitivity issue. Therefore, there are many open questions to be addressed by electron microscopy. For example, it has been proposed that perovskites undergo phase changes at certain temperatures, and to probing such phase changes at the atomic level with *in situ* characterization at the single-particle level will provide important insights. Another important question to be addressed is the 3D atomic imaging of perovskite NCs and this can solve the issues associated with the crystallinity of perovskite NCs. In addition, electron microscopy could play an important role in identifying the location of dopants in doped perovskite NCs. On the author hand, X-ray scattering techniques have been used extensively to characterize the crystallinity of bulk and NC perovskites. X-rays have previously been used to study the nucleation and growth mechanism of metal NCs. Extending such studies to perovskite NCs would

improve the understanding of their growth process. In addition, small-angle X-ray scattering techniques could help us unfold the assembly of ligand molecules on the surface of perovskite NCs.

Outstanding Questions in Optical Properties of MP NCs.

Perovskites have become popular for their interesting properties. Unlike classical QDs, perovskite NCs exhibit extremely high PLQY without having any shell on their surface. This is attributed to the shallow character of the defect-related energy states, which enables defect tolerance, that is, low nonradiative recombination rates despite high densities of defects. However, recent studies have shown that the surface traps generated by the detachment of ligands and surface atoms from perovskite NCs can have a drastic effect on their PLQY. It appears therefore that the nature of surface traps is not yet fully understood. The energy and nature of the traps created by the detached ligands need to be assessed, especially since the traps created may not follow thermodynamic predictions. In addition, the role of ligands on the optical properties of perovskite NCs has not been investigated in detail. In particular, ligands can significantly influence the optical properties of thinner nanostructures such as NPLs and ultrathin NWs. One of the ongoing debates about light emission in LHP NCs is the exciton fine structure, which governs the radiative *versus* nonradiative recombination rates significantly. Although initially it was believed that the lowest exciton state of LHP NCs is bright, while the highest exciton state is dark, later investigations suggested the opposite. As transition metal ion doping in LHP NCs has been gaining increasing attention, more in-depth understanding is needed on how the crystal field resulting from doping induces the splitting of bright *versus* dark excitonic states. On the other hand, 0D non-perovskites, and Pb-free perovskites are emerging as potential semiconducting materials for white light generation from self-trapped excitons. However, the formation of self-trapped excitons and the photophysics in such materials is still not well-understood. Very recently, chiral perovskite NCs have been receiving significant attention due to their polarized emission. In most cases, chirality in perovskites is induced by chiral ligands. However, the origin of the induced chirality in perovskites is still under debate. Several mechanisms, such as chiral molecules-induced symmetry breaking in the crystal lattice, dipolar interactions between chiral molecules and perovskites, and spin-orbit coupling, have been proposed for the origin of chirality, and these need further in-depth investigations in the future.

Another important phenomenon of MHP NCs that requires further understanding is photoluminescence intermittency, which is also known as “blinking”. This limits the application of these materials in quantum optical devices. Single-particle investigations of MHP NCs suggest that this effect is intrinsic to the materials, rather than the effect of the processing route, and it has been found that blinking occurs not only in quantum-confined systems but also in microcrystals. Several mechanisms have been put forward to explain how blinking occurs. These include the effects of photocharging and Auger recombination, or the effects of nonradiative recombination centers that could be metastable. However, further work is needed to understand how metastable defects could be activated/deactivated, and whether light could play a role. The density of these metastable defects also needs to be more reliably measured. In addition to blinking, single-particle investigations have also shown that electron–phonon coupling

in MHP NCs affects the emission spectra, leading to extra PL peaks. However, there is debate in the literature as to the degree of coupling between electrons and optical *versus* acoustic phonons. Furthermore, understanding into these phenomena could lead to insights of how charge transport could be improved.

Applications. MHP NCs have gained significant attention for applications involving optical emission and absorption. These include lasing, in which MHP NCs could lead to cost-effective solid-state lasers with emissions wavelengths that can be easily tuned. Here, we foresee three key challenges. First, the MHP NCs are unstable to heat and environmental stress, and require encapsulation strategies (e.g., NCs embedded in a glass matrix or in a Cs_4PbBr_6 matrix). Second, most work has been on Pb-based materials, and nontoxic alternatives that are air-stable need to be developed. These include double perovskites, but the PLQY in many lead-free alternatives have not matched the near-unity values the Pb-based NCs can be routinely obtained (as discussed above). Third, lasing in MHPs has only been achieved through optical pumping. Electrical pumping has been elusive, due to Auger recombination at high injection rates and the long-chain ligands used with NCs.

On the other hand, electrically driven spontaneous emission from MHP NCs has been achieved, and efficient LEDs based on lead-halide perovskite NCs have been demonstrated, with EQEs exceeding 20% after only 5 years of development. Perovskite LEDs also have the advantages of high-color purity, ultrawide color gamut, potential for low materials and fabrication costs, as well as compatibility with the existing manufacturing technology for OLEDs/QD-LEDs. Thus far, most efforts have focused on improving the EQEs of perovskite LEDs. However, it is also important to develop an understanding behind these improvements in performance, which will be important for rationally achieving further increases in efficiency. It will also be important to scale-up perovskite LEDs from the mm-level to large-area displays with nanometer-level uniformity in terms of NC size and emission wavelength. The stability of perovskite LEDs needs to be improved, particularly under operation. Furthermore, the development of perovskite LEDs has been focused on green, red, and near-infrared emitters, which have achieved the highest EQEs (of >20%). More recently, there have been significant efforts to develop blue emitters, owing to their importance for full-color displays, but both the EQE and stability lag behind their green and near-infrared counterparts. Beyond these challenges, it will also be important to replicate the high performance of lead-halide perovskites in lead-free alternatives. Currently, this is challenging because Sn- and Ge-based perovskites are less stable than the Pb-based perovskites, and many of other materials that have been proposed as alternatives have indirect band gaps and low PLQYs.

MHPs are promising for photodetectors and radiation detectors due to their high optical absorption coefficients, high Z numbers (ensuring strong attenuation of radiation) and long diffusion lengths. In photodetectors, NCs with reduced defect density have been achieved, leading to devices with high on/off ratios for the photocurrent exceeding 10^5 . Nanostructured perovskites have also been realized in 1D and 2D structures and combined with carbon nanotubes or 2D materials to demonstrate enhanced performance. In radiation detectors, NCs have shown promise for X-ray scintillators,

which rapid response times and low X-ray detection limits demonstrated.

Furthermore, perovskites have been explored for FETs, where the ambipolar nature of charge transport could offer interesting possibilities. However, one of the important challenges to overcome is the low field-effect mobility, which arises in part from ion migration. Passivating surface defects in NCs may aid in addressing this.

Perovskite NCs have also demonstrated significant promise in solar cells, with PCEs >16% achieved, which represents the highest efficiencies for any QD-based solar cell. NCs offer the advantage of stabilizing metastable phases, such as the α -phase of CsPbI_3 , which led to >10% efficient devices. NCs in particular offer the important advantage of high PLQYs, which result in low nonradiative losses. The open-circuit voltages of NC perovskite solar cells have therefore been closer to the radiative limits than bulk thin film perovskites. The NCs are also amenable to alloying, and the most efficient NC perovskite solar cells use a mixture of Cs and FA in the A-site, which leads to a smaller band gap than pure Cs-based perovskites. Finally, perovskite NCs have just started to receive significant attention as photosensitizers in photocatalysis. Perovskite photocatalysis has already been demonstrated for H_2 evolution, CO_2 reduction, the degradation of organic pollutants and selective organic synthesis. However, the field is still young, and there are still many possibilities that remain to be explored. Some of the challenges include enhancing stability and performance as well as developing more effective encapsulation strategies.

ASSOCIATED CONTENT

SI Supporting Information

The Supporting Information is available free of charge at <https://pubs.acs.org/doi/10.1021/acsnano.0c08903>.

Movie S1: Synthesis of MAPbBr_3 NCs by ligand-assisted reprecipitation method ([MP4](#))

Movie S2: Degradation of a CsPbBr_3 nanocube upon continuous scanning of the electron beam ([MPG](#))

Movie S3: Large-scale synthesis of CsPbBr_3 nanocubes ([MP4](#))

HAADF-STEM images of CsPbBr_3 nanocubes acquired under continuous electron beam illumination ([PDF](#))

AUTHOR INFORMATION

Corresponding Authors

Robert L. Z. Hoye – Department of Materials, Imperial College London, London SW7 2AZ, United Kingdom;  orcid.org/0000-0002-7675-0065; Email: r.hoye@imperial.ac.uk

Lakshminarayana Polavarapu – Chair for Photonics and Optoelectronics, Nano-Institute Munich, Department of Physics, Ludwig-Maximilians-Universität (LMU), 80539 Munich, Germany; CINBIO, Universidade de Vigo, Materials Chemistry and Physics group, Departamento de Química Física, 36310 Vigo, Spain;  orcid.org/0000-0002-9040-5719; Email: lakshmi@uvigo.es, l.polavarapu@lmu.de

Authors

Amrita Dey – Chair for Photonics and Optoelectronics, Nano-Institute Munich, Department of Physics, Ludwig-Maximilians-Universität (LMU), 80539 Munich, Germany;  orcid.org/0000-0003-2372-2172

Junzhi Ye — Cavendish Laboratory, University of Cambridge, Cambridge CB3 0HE, United Kingdom

Apurba De — School of Chemistry, University of Hyderabad, Hyderabad 500 046, India; orcid.org/0000-0002-3042-0642

Elke Debroye — Department of Chemistry, KU Leuven, 3001 Leuven, Belgium; orcid.org/0000-0003-1087-4759

Seung Kyun Ha — Department of Chemical Engineering, Massachusetts Institute of Technology, Cambridge, Massachusetts 02139, United States; orcid.org/0000-0003-2967-1097

Eva Bladt — EMAT, University of Antwerp, 2020 Antwerp, Belgium; NANOLab Center of Excellence, University of Antwerp, 2020 Antwerp, Belgium

Anuraj S. Kshirsagar — Department of Chemistry, Indian Institute of Science Education and Research (IISER), Pune 411008, India

Ziyu Wang — School of Science and Technology for Optoelectronic Information, Yantai University, Yantai, Shandong Province 264005, China

Jun Yin — CINBIO, Universidad de Vigo, Materials Chemistry and Physics group, Departamento de Química Física, 36310 Vigo, Spain; Advanced Membranes and Porous Materials Center and Division of Physical Science and Engineering, King Abdullah University of Science and Technology, Thuwal 23955-6900, Kingdom of Saudi Arabia; orcid.org/0000-0002-1749-1120

Yue Wang — MIIT Key Laboratory of Advanced Display Materials and Devices, Institute of Optoelectronics & Nanomaterials, College of Materials Science and Engineering, Nanjing University of Science and Technology, Nanjing 210094, China

Li Na Quan — Department of Chemistry, University of California, Berkeley, Berkeley, California 94720, United States; Materials Sciences Division, Lawrence Berkeley National Laboratory, Berkeley, California 94720, United States

Fei Yan — LUMINOUS! Center of Excellence for Semiconductor Lighting and Displays, TPI-The Photonics Institute, School of Electrical and Electronic Engineering, Nanyang Technological University, Singapore 639798

Mengyu Gao — Materials Sciences Division, Lawrence Berkeley National Laboratory, Berkeley, California 94720, United States; Department of Materials Science and Engineering, University of California, Berkeley, California 94720, United States; orcid.org/0000-0003-1385-7364

Xiaoming Li — MIIT Key Laboratory of Advanced Display Materials and Devices, Institute of Optoelectronics & Nanomaterials, College of Materials Science and Engineering, Nanjing University of Science and Technology, Nanjing 210094, China

Javad Shamsi — Cavendish Laboratory, University of Cambridge, Cambridge CB3 0HE, United Kingdom; orcid.org/0000-0003-4684-5407

Tushar Debnath — Chair for Photonics and Optoelectronics, Nano-Institute Munich, Department of Physics, Ludwig-Maximilians-Universität (LMU), 80539 Munich, Germany; orcid.org/0000-0002-8108-4482

Muhan Cao — Institute of Functional Nano & Soft Materials (FUNSOM), Jiangsu Key Laboratory for Carbon-Based Functional Materials and Devices, Soochow University, Suzhou 215123, China; orcid.org/0000-0002-7988-7219

Manuel A. Scheel — Lehrstuhl für Funktionelle Materialien, Physik Department, Technische Universität München, 85748 Garching, Germany; orcid.org/0000-0003-0508-6694

Sudhir Kumar — Institute for Chemical and Bioengineering, Department of Chemistry and Applied Biosciences, ETH-Zurich, CH-8093 Zürich, Switzerland; orcid.org/0000-0002-2994-7084

Julian A. Steele — MACS Department of Microbial and Molecular Systems, KU Leuven, 3001 Leuven, Belgium; orcid.org/0000-0001-7982-4413

Marina Gerhard — Chemical Physics and NanoLund, Lund University, 22100 Lund, Sweden

Lata Chouhan — Graduate School of Environmental Science and Research Institute for Electronic Science, Hokkaido University, Sapporo, Hokkaido 001-0020, Japan

Ke Xu — Department of Chemistry and Biochemistry, University of California, Santa Cruz, California 95064, United States; Multiscale Crystal Materials Research Center, Shenzhen Institute of Advanced Technology, Chinese Academy of Sciences, Shenzhen 518055, China

Xian-gang Wu — Beijing Key Laboratory of Nanophotonics and Ultrafine Optoelectronic Systems, School of Materials Science & Engineering, Beijing Institute of Technology, Beijing 100081, China

Yanxiu Li — Department of Materials Science and Engineering, and Centre for Functional Photonics (CFP), City University of Hong Kong, Kowloon, Hong Kong S.A.R.

Yangning Zhang — McKetta Department of Chemical Engineering and Texas Materials Institute, The University of Texas at Austin, Austin, Texas 78712-1062, United States; orcid.org/0000-0001-5511-955X

Anirban Dutta — School of Materials Sciences, Indian Association for the Cultivation of Science, Kolkata 700032, India; orcid.org/0000-0001-9915-6985

Chuang Han — Department of Chemistry and Biochemistry, San Diego State University, San Diego, California 92182, United States

Ilka Vincon — Chair for Photonics and Optoelectronics, Nano-Institute Munich, Department of Physics, Ludwig-Maximilians-Universität (LMU), 80539 Munich, Germany

Andrey L. Rogach — Department of Materials Science and Engineering, and Centre for Functional Photonics (CFP), City University of Hong Kong, Kowloon, Hong Kong S.A.R.; orcid.org/0000-0002-8263-8141

Angshuman Nag — Department of Chemistry, Indian Institute of Science Education and Research (IISER), Pune 411008, India; orcid.org/0000-0003-2308-334X

Anunay Samanta — School of Chemistry, University of Hyderabad, Hyderabad 500 046, India; orcid.org/0000-0003-1551-0209

Brian A. Korgel — McKetta Department of Chemical Engineering and Texas Materials Institute, The University of Texas at Austin, Austin, Texas 78712-1062, United States; orcid.org/0000-0001-6242-7526

Chih-Jen Shih — Institute for Chemical and Bioengineering, Department of Chemistry and Applied Biosciences, ETH-Zurich, CH-8093 Zürich, Switzerland; orcid.org/0000-0002-5258-3485

Daniel R. Gamelin — Department of Chemistry, University of Washington, Seattle, Washington 98195, United States; orcid.org/0000-0003-2888-9916

Dong Hee Son — Department of Chemistry, Texas A&M University, College Station, Texas 77843, United States

Haibo Zeng — MIIT Key Laboratory of Advanced Display Materials and Devices, Institute of Optoelectronics & Nanomaterials, College of Materials Science and Engineering, Nanjing University of Science and Technology, Nanjing 210094, China;  orcid.org/0000-0002-0281-3617

Haizheng Zhong — Beijing Key Laboratory of Nanophotonics and Ultrafine Optoelectronic Systems, School of Materials Science & Engineering, Beijing Institute of Technology, Beijing 100081, China;  orcid.org/0000-0002-2662-7472

Handong Sun — Division of Physics and Applied Physics, School of Physical and Mathematical Sciences and Centre for Disruptive Photonic Technologies (CDPT), Nanyang Technological University, Singapore 637371;  orcid.org/0000-0002-2261-7103

Hilmi Volkan Demir — LUMINOUS! Center of Excellence for Semiconductor Lighting and Displays, TPI-The Photonics Institute, School of Electrical and Electronic Engineering and Division of Physics and Applied Physics, School of Physical and Mathematical Sciences, Nanyang Technological University, Singapore 639798; Department of Electrical and Electronics Engineering, Department of Physics, UNAM-Institute of Materials Science and Nanotechnology, Bilkent University, Ankara 06800, Turkey;  orcid.org/0000-0003-1793-112X

Ivan G. Scheblykin — Chemical Physics and NanoLund, Lund University, 22100 Lund, Sweden;  orcid.org/0000-0001-6059-4777

Íván Mora-Seró — Institute of Advanced Materials (INAM), Universitat Jaume I, 12071 Castelló, Spain;  orcid.org/0000-0003-2508-0994

Jacek K. Stolarczyk — Chair for Photonics and Optoelectronics, Nano-Institute Munich, Department of Physics, Ludwig-Maximilians-Universität (LMU), 80539 Munich, Germany;  orcid.org/0000-0001-7935-4204

Jin Z. Zhang — Department of Chemistry and Biochemistry, University of California, Santa Cruz, California 95064, United States;  orcid.org/0000-0003-3437-912X

Jochen Feldmann — Chair for Photonics and Optoelectronics, Nano-Institute Munich, Department of Physics, Ludwig-Maximilians-Universität (LMU), 80539 Munich, Germany

Johan Hofkens — Department of Chemistry, KU Leuven, 3001 Leuven, Belgium; Max Planck Institute for Polymer Research, Mainz 55128, Germany;  orcid.org/0000-0002-9101-0567

Joseph M. Luther — National Renewable Energy Laboratory, Golden, Colorado 80401, United States;  orcid.org/0000-0002-4054-8244

Julia Pérez-Prieto — Institute of Molecular Science, University of Valencia, Valencia 46980, Spain;  orcid.org/0000-0002-5833-341X

Liang Li — School of Environmental Science and Engineering, Shanghai Jiao Tong University, Shanghai 200240, China;  orcid.org/0000-0003-3898-0641

Liberato Manna — Nanochemistry Department, Istituto Italiano di Tecnologia, Genova 16163, Italy;  orcid.org/0000-0003-4386-7985

Maryna I. Bodnarchuk — Institute of Inorganic Chemistry and § Institute of Chemical and Bioengineering, Department of Chemistry and Applied Bioscience, ETH Zurich, CH-8093 Zürich, Switzerland; Laboratory for Thin Films and Photovoltaics, Empa—Swiss Federal Laboratories for Materials Science and Technology, CH-8600 Dübendorf, Switzerland;  orcid.org/0000-0001-6597-3266

Maksym V. Kovalenko — Institute of Inorganic Chemistry and § Institute of Chemical and Bioengineering, Department of Chemistry and Applied Bioscience, ETH Zurich, CH-8093 Zürich, Switzerland; Laboratory for Thin Films and Photovoltaics, Empa—Swiss Federal Laboratories for Materials Science and Technology, CH-8600 Dübendorf, Switzerland;  orcid.org/0000-0002-6396-8938

Maarten B. J. Roeffaers — MACS Department of Microbial and Molecular Systems, KU Leuven, 3001 Leuven, Belgium;  orcid.org/0000-0001-6582-6514

Narayan Pradhan — School of Materials Sciences, Indian Association for the Cultivation of Science, Kolkata 700032, India;  orcid.org/0000-0003-4646-8488

Omar F. Mohammed — Advanced Membranes and Porous Materials Center and KAUST Catalysis Center, King Abdullah University of Science and Technology, Thuwal 23955-6900, Kingdom of Saudi Arabia;  orcid.org/0000-0001-8500-1130

Osman M. Bakr — Advanced Membranes and Porous Materials Center and Division of Physical Science and Engineering, King Abdullah University of Science and Technology, Thuwal 23955-6900, Kingdom of Saudi Arabia;  orcid.org/0000-0002-3428-1002

Peidong Yang — Department of Chemistry, University of California, Berkeley, Berkeley, California 94720, United States; Materials Sciences Division, Lawrence Berkeley National Laboratory, Berkeley, California 94720, United States; Department of Materials Science and Engineering, University of California, Berkeley, California 94720, United States; Kavli Energy NanoScience Institute, Berkeley, California 94720, United States;  orcid.org/0000-0003-4799-1684

Peter Müller-Buschbaum — Lehrstuhl für Funktionelle Materialien, Physik Department, Technische Universität München, 85748 Garching, Germany; Heinz Maier-Leibnitz Zentrum (MLZ), Technische Universität München, D-85748 Garching, Germany;  orcid.org/0000-0002-9566-6088

Prashant V. Kamat — Notre Dame Radiation Laboratory, Department of Chemistry and Biochemistry, University of Notre Dame, Notre Dame, Indiana 46556, United States;  orcid.org/0000-0002-2465-6819

Qiaoliang Bao — Department of Materials Science and Engineering and ARC Centre of Excellence in Future Low-Energy Electronics Technologies (FLEET), Monash University, Clayton, Victoria 3800, Australia;  orcid.org/0000-0002-6971-789X

Qiao Zhang — Institute of Functional Nano & Soft Materials (FUNSOM), Jiangsu Key Laboratory for Carbon-Based Functional Materials and Devices, Soochow University, Suzhou 215123, China;  orcid.org/0000-0001-9682-3295

Roman Krahne — Istituto Italiano di Tecnologia, 16163 Genova, Italy;  orcid.org/0000-0003-0066-7019

Raquel E. Galian — School of Environmental Science and Engineering, Shanghai Jiao Tong University, Shanghai 200240, China;  orcid.org/0000-0001-8703-4403

Samuel D. Stranks — Cavendish Laboratory, University of Cambridge, Cambridge CB3 0HE, United Kingdom; Department of Chemical Engineering and Biotechnology, University of Cambridge, Cambridge CB3 0AS, United Kingdom;  orcid.org/0000-0002-8303-7292

Sara Bals — EMAT, University of Antwerp, 2020 Antwerp, Belgium; NANOLab Center of Excellence, University of

Antwerp, 2020 Antwerp, Belgium; orcid.org/0000-0002-4249-8017

Vasudevanpillai Biju – Graduate School of Environmental Science and Research Institute for Electronic Science, Hokkaido University, Sapporo, Hokkaido 001-0020, Japan; orcid.org/0000-0003-3650-9637

William A. Tisdale – Department of Chemical Engineering, Massachusetts Institute of Technology, Cambridge, Massachusetts 02139, United States; orcid.org/0000-0002-6615-5342

Yong Yan – Department of Chemistry and Biochemistry, San Diego State University, San Diego, California 92182, United States

Complete contact information is available at:
<https://pubs.acs.org/10.1021/acsnano.0c08903>

Author Contributions

L.P. initiated and coordinated the review. L.P., R.L.Z.H., and L.M. edited the manuscript. The manuscript was written through contributions of all authors. L.P. contributed to the introduction; L.P., H.Z., and M.V.K. contributed to the general synthesis methods; L.P. contributed to the synthesis of nanocubes; B.A.K. and Y.Z. contributed purification of nanocubes; W.A.T. and S.K.H. contributed synthesis of nanoplatelets; P.Y., L.N.Q., and M.G. contributed synthesis and self-assembly of nanowires; L.P., H. Zhong, and X.G.W. contributed to the *in situ* synthesis; L.M., R.K., and P.V.K. contributed to the sections on synthesis by ion exchange; R.K. and L.P. contributed post-synthetic shape transformations; J.P.P., R.E.G., H. Zeng, X.L., J.Z., and K.X. contributed surface chemistry and post-synthetic surface passivation; O.M.B., O.F.M., and J.Y. contributed synthesis of 0D nonperovskites; Q.Z., M.C., A.L.R., Y.L., and L.L. contributed surface coating strategies; D.H.S., D.R.G., L.P., N.P., and An. D. contributed synthesis by doping; A.N., A.S.K., R.L.Z.H., J.S., and L.P. contributed synthesis of Pb-free NCs; L.P., and M.Y.B. contributed self-assembly into superlattices; L.P., J.F., and I.V. contributed chiral perovskite NCs; Am.D., J.K.S., J.F., A.S., and Ap.D. contributed linear optical properties, charge carrier dynamics and charge-transfer studies; E.D., J.H., M.B.J.R., J.A.S., V.B., L.C., I.G.S., and M.G. contributed single particle studies; E.B. and S.B. contributed electron microscopy characterization; P.M.-B. and M.A.S. contributed X-ray scattering characterization; H.S., H. Zeng, and Y.W. contributed lasing in perovskite NCs; H.V.D., Y.F., R.L.Z.H., J.Y., S.D.S., J.S., C.J.S., and S.K. contributed LEDs section; Q.B. and Z.W. contributed photodetectors and FETs; T.D., Y.Y., and C.H. contributed photocatalysis section; J.M.L. and I.M.S. contributed solar cell section. All authors read the manuscript and have given approval to the final version of the manuscript.

Notes

The authors declare no competing financial interest.

ACKNOWLEDGMENTS

L.P. acknowledges support from the Spanish Ministerio de Ciencia e Innovación through Ramón y Cajal grant (RYC2018-026103-I). A.D., T.D., I.V., J.K.S., J.F., M.A.S., P.M.-B. and L.P. acknowledge financial support by the Bavarian State Ministry of Science, Research, and Arts through the grant “Solar Technologies go Hybrid (SolTech)” and by the Deutsche Forschungsgemeinschaft (DFG, German Research Foundation) under Germany’s Excellence Strategy—EXC

2089/1—390776260 (“e-conversion”). J.F., L.P., and V.D. acknowledge support by LMU’s “Singapore Initiative” funded within the German Excellence Strategy. H. Zeng acknowledges the support of NSFC (61874054, 51902160), the Natural Science Foundation of Jiangsu Province (BK20180489), Young Elite Scientists Sponsorship Program by CAST (2018QNRC001), Fundamental Research Funds for the Central Universities (30918011208), and the National Natural Science Funds for Distinguished Young Scholars (61725402). Z.W. acknowledges the support of the Natural Science Foundation of Shandong Province, China. (ZR2020QE051). B.A.K. and Y.Z. acknowledge funding of this work by the Robert A. Welch Foundation (Grant No. F-1464). H.S. acknowledges the support of Ministry of Education Singapore through the Academic Research Fund under Projects MOE Tier 1, RG 189/17 and RG RG95/19 as well as Tier 2 MOE2016-T2-1-054. H.V.D. and Y.F. gratefully acknowledge TUBA and support in part from NRF-NRFI2016-08 and A*STAR SERC Pharos 52 73 00025. Y.W. thanks the support by the Natural Science Foundation of Jiangsu Province (BK20190446) and NSFC (11904172). J.P.P. and R.E.G. acknowledge the support of Ministerio de Economía, Industria y Competitividad (CTQ2017-82711-P and MDM-2015-0538, partially cofinanced with Fondo Europeo de Desarrollo Regional and Agencia Estatal de Investigación) and Generalitat Valenciana (IDIFEDER/2018/064 and PROMETEO/2018/138, partially cofinanced with Fondo Europeo de Desarrollo Regional). E.D. and J.H. acknowledge financial support from the Research Foundation—Flanders (FWO Grant Nos. S002019N, G.0B39.15, G.0B49.15, G.0962.13, G098319N, and ZW15_09-GOH6316), the Research Foundation—Flanders postdoctoral fellowships to J.A.S. and E.D. (FWO Grant Nos. 12Y7218N and 12O3719N, respectively), the KU Leuven Research Fund (C14/15/053 and C14/19/079), the Flemish government through long-term structural funding Methusalem (CASAS2, Meth/15/04), the Hercules Foundation (HER/11/14), iBOF funding (PERsist: iBOF-21-085), the Swedish Research Council (VR 2016-04433), Knut and Alice Wallenberg Foundation (KAW 2016.0059), MEXT JSPS Grant-in-Aid for Scientific Research B (19H02550) and Specially Promoted Research (18H05205). R.L.Z.H. acknowledges support from the Royal Academy of Engineering through the Research Fellowship scheme (No. RF\201718\1701) and Downing College Cambridge through the Kim and Julian Silverman Research Fellowship. M.G. acknowledges a Wenner-Gren fellowship (UPD2017-0223), and L.C. acknowledges a JICA fellowship. A.S. acknowledges the J.C. Bose Fellowship of the Science and Engineering Research Board (SERB). A.L.R. acknowledges the Croucher Foundation of Hong Kong. J.M.L. and Y.Y. acknowledge support from the U.S. Department of Energy, Office of Basic Energy Sciences through the Energy Frontier Research Center, Center for Hybrid Organic Inorganic Semiconductors for Energy (CHOISE). S.K.H. and W.A.T. were supported by the U.S. Department of Energy, Office of Science, Basic Energy Sciences under Award No. DE-SC0019345. A.L.R. acknowledges the Croucher Foundation of Hong Kong SAR and the Research Grant Council of Hong Kong SAR (GRF 17301520). J.Z.Z. is grateful to financial support from the US NSF (CHE-1904547). A.D. and T.D. acknowledge post-doctoral research fellowship support from Alexander von Humboldt foundation. I.M.-S. acknowledges the financial support from Ministry of Science and Innovation of Spain under Project STABLE (PID2019-107314RB-I00) and

Generalitat Valenciana *via* Prometeo Grant Q-Devices (Prometeo/2018/098). P.V.K. acknowledges the support of the Division of Chemical Sciences, Geosciences, and Biosciences, Office of Basic Energy Sciences of the U.S. Department of Energy, through award (award DE-FC02-04ER15533). S.D.S. acknowledges the Royal Society and Tata Group (UF150033) and the EPSRC (EP/R023980/1). The work has received funding from the European Research Council under the European Union's Horizon 2020 research and innovation programme (HYPERION - grant agreement no. 756962). D.R.G. acknowledges support from the US NSF (DMR-1807394) P.Y., L.N.Q., and M.G. acknowledge the funding from U. S. Department of Energy, Office of Science, Office of Basic Energy Sciences, Materials Sciences and Engineering Division, under Contract No. DE-AC02-05-CH11231 within the Physical Chemistry of Inorganic Nanostructures Program (KC3103). M.B. acknowledges funding from the Swiss National Science Foundation (Grant No. 200021_192308, "Q-Light - Engineered Quantum Light Sources with Nanocrystal Assemblies"). L.M. acknowledges funding from the FLAG-ERA JTC2019 project PeroGas.

VOCABULARY

halide perovskites, a family of materials with the basic chemical formula ABX_3 , in which A and B are cations, and X is a halide ion; the perovskite family can be extended by combining two different A-site cations or two B-site cations or by combining vacancies (giving rise to vacancy-ordered perovskites); **quantum confinement**, localization of electrons and holes into a narrow space with dimension comparable to or smaller than the Bohr radius, leading to the increased coupling between electron–hole pairs and their energy levels becoming discrete and controllable by the size of the material; quantum confinement can be achieved along one dimension (nanoplatelets), two dimensions (nanowires), and three dimensions (quantum dots); **zwitterionic ligand**, chemical species (usually comprising a carbon backbone) with both positively and negatively charged functional groups that can bind to the surface of NCs; **surface passivation**, a surface treatment process that can reduce unwanted carrier recombination process by eliminating defects on the surface of the materials for improving their optoelectronic properties such as photoluminescent quantum yield and carrier lifetime; **superlattice or supercrystals**, long-range-ordered array of nano- and microparticles; **photoluminescence blinking (or intermittency)**, stochastic fluctuations in photoluminescence intensity; **electroluminescence**, spontaneous emission obtained through the injection of electrons and holes into an emissive layer

REFERENCES

- (1) Wells, H. L. Über die Cäsium- und Kalium-Bleihalogenide. *Zeitschrift für anorganische Chemie* **1893**, *3*, 195–210.
- (2) Weber, D. Das Perowskitesystem $CH_3NH_3[PbSn_{1-n}X_3]$ (X = Cl, Br, I) / The Perovskite System $CH_3NH_3[Pb_xSn_{1-n}X_3]$ (X = Cl, Br, I). *Z. Naturforsch., B: J. Chem. Sci.* **1979**, *34*, 939–941.
- (3) Weber, D. $CH_3NH_3PbX_3$, ein Pb(II)-System mit kubischer Perowskitstruktur / $CH_3NH_3PbX_3$, a Pb(II)-System with Cubic Perovskite Structure. *Z. Naturforsch., B: J. Chem. Sci.* **1978**, *33*, 1443–1445.
- (4) Weber, D. $CH_3NH_3SnBr_xI_{3-x}$ (x = 0–3), ein Sn(II)-System mit kubischer Perowskitstruktur / $CH_3NH_3SnBr_xI_{3-x}$ (x = 0–3), a Sn(II)-System with Cubic Perovskite Structure. *Z. Naturforsch., B: J. Chem. Sci.* **1978**, *33*, 862–865.

- (5) Mitzi, D. B.; Chondroudis, K.; Kagan, C. R. Organic-Inorganic Electronics. *IBM J. Res. Dev.* **2001**, *45*, 29–45.
- (6) Mitzi, D. B.; Feild, C. A.; Harrison, W. T. A.; Guloy, A. M. Conducting Tin Halides with a Layered Organic-Based Perovskite Structure. *Nature* **1994**, *369*, 467–469.
- (7) Kojima, A.; Teshima, K.; Shirai, Y.; Miyasaka, T. Organometal Halide Perovskites as Visible-Light Sensitizers for Photovoltaic Cells. *J. Am. Chem. Soc.* **2009**, *131*, 6050–6051.
- (8) Kim, H.-S.; Lee, C.-R.; Im, J.-H.; Lee, K.-B.; Moehl, T.; Marchioro, A.; Moon, S.-J.; Humphry-Baker, R.; Yum, J.-H.; Moser, J. E.; Grätzel, M.; Park, N.-G. Lead Iodide Perovskite Sensitized All-Solid-State Submicron Thin Film Mesoscopic Solar Cell with Efficiency Exceeding 9%. *Sci. Rep.* **2012**, *2*, 591.
- (9) Lee, M. M.; Teuscher, J.; Miyasaka, T.; Murakami, T. N.; Snaith, H. J. Efficient Hybrid Solar Cells Based on Meso-Superstructured Organometal Halide Perovskites. *Science* **2012**, *338*, 643–647.
- (10) Manser, J. S.; Christians, J. A.; Kamat, P. V. Intriguing Optoelectronic Properties of Metal Halide Perovskites. *Chem. Rev.* **2016**, *116*, 12956–13008.
- (11) Xing, G.; Mathews, N.; Sun, S.; Lim, S. S.; Lam, Y. M.; Grätzel, M.; Mhaisalkar, S.; Sum, T. C. Long-Range Balanced Electron- and Hole-Transport Lengths in Organic-Inorganic $CH_3NH_3PbI_3$. *Science* **2013**, *342*, 344–347.
- (12) National Renewable Energy Laboratory Best Research-Cell Efficiency Chart; <https://www.nrel.gov/pv/assets/pdfs/best-research-cell-efficiencies.20200803.pdf> (accessed September 19, 2020).
- (13) Stranks, S. D.; Eperon, G. E.; Grancini, G.; Menelaou, C.; Alcocer, M. J.; Leijtens, T.; Herz, L. M.; Petrozza, A.; Snaith, H. J. Electron-Hole Diffusion Lengths Exceeding 1 Micrometer in an Organometal Trihalide Perovskite Absorber. *Science* **2013**, *342*, 341–344.
- (14) Protesescu, L.; Yakunin, S.; Bodnarchuk, M. I.; Krieg, F.; Caputo, R.; Hendon, C. H.; Yang, R. X.; Walsh, A.; Kovalenko, M. V. Nanocrystals of Cesium Lead Halide Perovskites ($CsPbX_3$, X = Cl, Br, and I): Novel Optoelectronic Materials Showing Bright Emission with Wide Color Gamut. *Nano Lett.* **2015**, *15*, 3692–3696.
- (15) de Quilettes, D. W.; Vorpahl, S. M.; Stranks, S. D.; Nagaoka, H.; Eperon, G. E.; Ziffer, M. E.; Snaith, H. J.; Ginger, D. S. Impact of Microstructure on Local Carrier Lifetime in Perovskite Solar Cells. *Science* **2015**, *348*, 683–686.
- (16) Sichert, J. A.; Tong, Y.; Mutz, N.; Vollmer, M.; Fischer, S.; Milowska, K. Z.; García Cortadella, R.; Nickel, B.; Cardenas-Daw, C.; Stolarczyk, J. K.; Urban, A. S.; Feldmann, J. Quantum Size Effect in Organometal Halide Perovskite Nanoplatelets. *Nano Lett.* **2015**, *15*, 6521–6527.
- (17) Dou, L.; Wong, A. B.; Yu, Y.; Lai, M.; Kornienko, N.; Eaton, S. W.; Fu, A.; Bischak, C. G.; Ma, J.; Ding, T.; Ginsberg, N. S.; Wang, L.-W.; Alivisatos, A. P.; Yang, P. Atomically Thin Two-Dimensional Organic-Inorganic Hybrid Perovskites. *Science* **2015**, *349*, 1518–1521.
- (18) Bekenstein, Y.; Koscher, B. A.; Eaton, S. W.; Yang, P.; Alivisatos, A. P. Highly Luminous Colloidal Nanoplates of Perovskite Cesium Lead Halide and Their Oriented Assemblies. *J. Am. Chem. Soc.* **2015**, *137*, 16008–16011.
- (19) Tyagi, P.; Arveson, S. M.; Tisdale, W. A. Colloidal Organohalide Perovskite Nanoplatelets Exhibiting Quantum Confinement. *J. Phys. Chem. Lett.* **2015**, *6*, 1911–1916.
- (20) Long, G.; Jiang, C.; Sabatini, R.; Yang, Z.; Wei, M.; Quan, L. N.; Liang, Q.; Rasmida, A.; Askerka, M.; Walters, G.; Gong, X.; Xing, J.; Wen, X.; Quintero-Bermudez, R.; Yuan, H.; Xing, G.; Wang, X. R.; Song, D.; Voznyy, O.; Zhang, M.; Hoogland, S.; Gao, W.; Xiong, Q.; Sargent, E. H. Spin Control in Reduced-Dimensional Chiral Perovskites. *Nat. Photonics* **2018**, *12*, 528–533.
- (21) Kovalenko, M. V.; Protesescu, L.; Bodnarchuk, M. I. Properties and Potential Optoelectronic Applications of Lead Halide Perovskite Nanocrystals. *Science* **2017**, *358*, 745–750.
- (22) Tong, Y.; Bohn, B. J.; Bladt, E.; Wang, K.; Müller-Buschbaum, P.; Bals, S.; Urban, A. S.; Polavarapu, L.; Feldmann, J. From Precursor Powders to $CsPbX_3$ Perovskite Nanowires: One-Pot Synthesis,

Growth Mechanism, and Oriented Self-Assembly. *Angew. Chem., Int. Ed.* **2017**, *56*, 13887–13892.

(23) Akkerman, Q. A.; Rainò, G.; Kovalenko, M. V.; Manna, L. Genesis, Challenges and Opportunities for Colloidal Lead Halide Perovskite Nanocrystals. *Nat. Mater.* **2018**, *17*, 394–405.

(24) Utzat, H.; Sun, W.; Kaplan, A. E. K.; Krieg, F.; Ginterseder, M.; Spokoyny, B.; Klein, N. D.; Shulenberger, K. E.; Perkinson, C. F.; Kovalenko, M. V.; Bawendi, M. G. Coherent Single-Photon Emission from Colloidal Lead Halide Perovskite Quantum Dots. *Science* **2019**, *363*, 1068–1072.

(25) Gonzalez-Carrero, S.; Galian, R. E.; Pérez-Prieto, J. Maximizing the Emissive Properties of $\text{CH}_3\text{NH}_3\text{PbBr}_3$ Perovskite Nanoparticles. *J. Mater. Chem. A* **2015**, *3*, 9187–9193.

(26) Park, Y.-S.; Guo, S.; Makarov, N. S.; Klimov, V. I. Room Temperature Single-Photon Emission from Individual Perovskite Quantum Dots. *ACS Nano* **2015**, *9*, 10386–10393.

(27) Song, J.; Li, J.; Li, X.; Xu, L.; Dong, Y.; Zeng, H. Quantum Dot Light-Emitting Diodes Based on Inorganic Perovskite Cesium Lead Halides (CsPbX_3). *Adv. Mater.* **2015**, *27*, 7162–7167.

(28) Wang, Y.; Li, X.; Song, J.; Xiao, L.; Zeng, H.; Sun, H. All-Inorganic Colloidal Perovskite Quantum Dots: A New Class of Lasing Materials with Favorable Characteristics. *Adv. Mater.* **2015**, *27*, 7101–7108.

(29) Zhang, F.; Zhong, H.; Chen, C.; Wu, X.-g.; Hu, X.; Huang, H.; Han, J.; Zou, B.; Dong, Y. Brightly Luminescent and Color-Tunable Colloidal $\text{CH}_3\text{NH}_3\text{PbX}_3$ ($\text{X} = \text{Br}, \text{I}, \text{Cl}$) Quantum Dots: Potential Alternatives for Display Technology. *ACS Nano* **2015**, *9*, 4533–4542.

(30) Tong, Y.; Bladt, E.; Agyüler, M. F.; Manzi, A.; Miłowska, K. Z.; Hintermayr, V. A.; Docampo, P.; Bals, S.; Urban, A. S.; Polavarapu, L.; Feldmann, J. Highly Luminescent Cesium Lead Halide Perovskite Nanocrystals with Tunable Composition and Thickness by Ultrasonication. *Angew. Chem., Int. Ed.* **2016**, *55*, 13887–13892.

(31) Tan, Z. K.; Moghaddam, R. S.; Lai, M. L.; Docampo, P.; Higler, R.; Deschler, F.; Price, M.; Sadhanala, A.; Pazos, L. M.; Credginton, D.; Hanusch, F.; Bein, T.; Snaith, H. J.; Friend, R. H. Bright Light-Emitting Diodes Based on Organometal Halide Perovskite. *Nat. Nanotechnol.* **2014**, *9*, 687–92.

(32) Green, M. A.; Ho-Baillie, A.; Snaith, H. J. The Emergence of Perovskite Solar Cells. *Nat. Photonics* **2014**, *8*, 506–514.

(33) Park, N.-G. Perovskite Solar Cells: An Emerging Photovoltaic Technology. *Mater. Today* **2015**, *18*, 65–72.

(34) Zhu, H.; Fu, Y.; Meng, F.; Wu, X.; Gong, Z.; Ding, Q.; Gustafsson, M. V.; Trinh, M. T.; Jin, S.; Zhu, X. Y. Lead Halide Perovskite Nanowire Lasers with Low Lasing Thresholds and High Quality Factors. *Nat. Mater.* **2015**, *14*, 636–642.

(35) Jung, H. S.; Park, N.-G. Perovskite Solar Cells: From Materials to Devices. *Small* **2015**, *11* (1), 10–25.

(36) Huang, H.; Polavarapu, L.; Sichert, J. A.; Susha, A. S.; Urban, A. S.; Rogach, A. L. Colloidal Lead Halide Perovskite Nanocrystals: Synthesis, Optical Properties and Applications. *NPG Asia Mater.* **2016**, *8*, e328–e328.

(37) Ramasamy, P.; Lim, D.-H.; Kim, B.; Lee, S.-H.; Lee, M.-S.; Lee, J.-S. All-Inorganic Cesium Lead Halide Perovskite Nanocrystals for Photodetector Applications. *Chem. Commun.* **2016**, *52*, 2067–2070.

(38) Xu, Y.-F.; Yang, M.-Z.; Chen, B.-X.; Wang, X.-D.; Chen, H.-Y.; Kuang, D.-B.; Su, C.-Y. A CsPbBr_3 Perovskite Quantum Dot/Graphene Oxide Composite for Photocatalytic CO_2 Reduction. *J. Am. Chem. Soc.* **2017**, *139*, 5660–5663.

(39) Lin, Y.-H.; Pattanasattayavong, P.; Anthopoulos, T. D. Metal-Halide Perovskite Transistors for Printed Electronics: Challenges and Opportunities. *Adv. Mater.* **2017**, *29*, 1702838.

(40) Van Le, Q.; Jang, H. W.; Kim, S. Y. Recent Advances toward High-Efficiency Halide Perovskite Light-Emitting Diodes: Review and Perspective. *Small Methods* **2018**, *2*, 1700419.

(41) Wei, Y.; Cheng, Z.; Lin, J. An Overview on Enhancing the Stability of Lead Halide perovskite Quantum Dots and their Applications in Phosphor-Converted LEDs. *Chem. Soc. Rev.* **2019**, *48*, 310–350.

(42) Chen, J.; Dong, C.; Idriss, H.; Mohammed, O. F.; Bakr, O. M. Metal Halide Perovskites for Solar-to-Chemical Fuel Conversion. *Adv. Energy Mater.* **2020**, *10*, 1902433.

(43) Dong, H.; Zhang, C.; Liu, X.; Yao, J.; Zhao, Y. S. Materials Chemistry and Engineering in Metal Halide Perovskite Lasers. *Chem. Soc. Rev.* **2020**, *49*, 951–982.

(44) Liu, S.; Guan, Y.; Sheng, Y.; Hu, Y.; Rong, Y.; Mei, A.; Han, H. A Review on Additives for Halide Perovskite Solar Cells. *Adv. Energy Mater.* **2020**, *10*, 1902492.

(45) Senanayak, S. P.; Abdi-Jalebi, M.; Kamboj, V. S.; Carey, R.; Shivanna, R.; Tian, T.; Schweicher, G.; Wang, J.; Giesbrecht, N.; Di Nuzzo, D.; Beere, H. E.; Docampo, P.; Ritchie, D. A.; Fairen-Jimenez, D.; Friend, R. H.; Sirringhaus, H. A General Approach for Hysteresis-Free, Operationally Stable Metal Halide Perovskite Field-Effect Transistors. *Sci. Adv.* **2020**, *6*, eaaz4948.

(46) Belykh, V. V.; Yakovlev, D. R.; Glazov, M. M.; Grigoryev, P. S.; Hussain, M.; Rautert, J.; Dirin, D. N.; Kovalenko, M. V.; Bayer, M. Coherent Spin Dynamics of Electrons and Holes in CsPbBr_3 Perovskite Crystals. *Nat. Commun.* **2019**, *10*, 673.

(47) Weidman, M. C.; Goodman, A. J.; Tisdale, W. A. Colloidal Halide Perovskite Nanoplatelets: An Exciting New Class of Semiconductor Nanomaterials. *Chem. Mater.* **2017**, *29*, 5019–5030.

(48) Akkerman, Q. A.; Motti, S. G.; Srimath Kandada, A. R.; Mosconi, E.; D’Innocenzo, V.; Bertoni, G.; Marras, S.; Kamino, B. A.; Miranda, L.; De Angelis, F.; Petrozza, A.; Prato, M.; Manna, L. Solution Synthesis Approach to Colloidal Cesium Lead Halide Perovskite Nanoplatelets with Monolayer-Level Thickness Control. *J. Am. Chem. Soc.* **2016**, *138*, 1010–6.

(49) Soe, C. M. M.; Nagabushana, G. P.; Shivaramaiah, R.; Tsai, H.; Nie, W.; Blancon, J.-C.; Melkonyan, F.; Cao, D. H.; Traoré, B.; Pedesseau, L.; Kepenekian, M.; Katan, C.; Even, J.; Marks, T. J.; Navrotsky, A.; Mohite, A. D.; Stoumpos, C. C.; Kanatzidis, M. G. Structural and Thermodynamic Limits of Layer Thickness in 2D Halide Perovskites. *Proc. Natl. Acad. Sci. U. S. A.* **2019**, *116*, 58–66.

(50) Fu, J.; Xu, Q.; Han, G.; Wu, B.; Huan, C. H. A.; Leek, M. L.; Sum, T. C. Hot Carrier Cooling Mechanisms in Halide Perovskites. *Nat. Commun.* **2017**, *8*, 1300.

(51) Travis, W.; Glover, E. N. K.; Bronstein, H.; Scanlon, D. O.; Palgrave, R. G. On the Application of the Tolerance Factor to Inorganic And Hybrid Halide Perovskites: A Revised System. *Chem. Sci.* **2016**, *7*, 4548–4556.

(52) Shamsi, J.; Urban, A. S.; Imran, M.; De Trizio, L.; Manna, L. Metal Halide Perovskite Nanocrystals: Synthesis, Post-Synthesis Modifications, and Their Optical Properties. *Chem. Rev.* **2019**, *119*, 3296–3348.

(53) Li, X.; Wu, Y.; Zhang, S.; Cai, B.; Gu, Y.; Song, J.; Zeng, H. CsPbX_3 Quantum Dots for Lighting and Displays: Room-Temperature Synthesis, Photoluminescence Superiorities, Underlying Origins and White Light-Emitting Diodes. *Adv. Funct. Mater.* **2016**, *26*, 2435–2445.

(54) Huang, H.; Li, Y.; Tong, Y.; Yao, E.-P.; Feil, M. W.; Richter, A. F.; Döblinger, M.; Rogach, A. L.; Feldmann, J.; Polavarapu, L. Spontaneous Crystallization of Perovskite Nanocrystals in Nonpolar Organic Solvents: A Versatile Approach for their Shape-Controlled Synthesis. *Angew. Chem., Int. Ed.* **2019**, *58*, 16558–16562.

(55) Nedelcu, G.; Protesescu, L.; Yakunin, S.; Bodnarchuk, M. I.; Grotevent, M. J.; Kovalenko, M. V. Fast Anion-Exchange in Highly Luminescent Nanocrystals of Cesium Lead Halide Perovskites (CsPbX_3 , $\text{X} = \text{Cl}, \text{Br}, \text{I}$). *Nano Lett.* **2015**, *15* (8), 5635–5640.

(56) Zhang, D. D.; Yang, Y. M.; Bekenstein, Y.; Yu, Y.; Gibson, N. A.; Wong, A. B.; Eaton, S. W.; Kornienko, N.; Kong, Q.; Lai, M. L.; Alivisatos, A. P.; Leone, S. R.; Yang, P. D. Synthesis of Composition Tunable and Highly Luminescent Cesium Lead Halide Nanowires through Anion-Exchange Reactions. *J. Am. Chem. Soc.* **2016**, *138*, 7236–7239.

(57) Akkerman, Q. A.; D’Innocenzo, V.; Accornero, S.; Scarpellini, A.; Petrozza, A.; Prato, M.; Manna, L. Tuning the Optical Properties of Cesium Lead Halide Perovskite Nanocrystals by Anion Exchange Reactions. *J. Am. Chem. Soc.* **2015**, *137*, 10276–10281.

(58) Murray, C. B.; Norris, D. J.; Bawendi, M. G. Synthesis and Characterization of Nearly Monodisperse CdE (E = Sulfur, Selenium, Tellurium) Semiconductor Nanocrystallites. *J. Am. Chem. Soc.* **1993**, *115*, 8706–8715.

(59) Zorman, B.; Ramakrishna, M. V.; Friesner, R. A. Quantum Confinement Effects in CdSe Quantum Dots. *J. Phys. Chem.* **1995**, *99*, 7649–7653.

(60) Bohn, B. J.; Tong, Y.; Gramlich, M.; Lai, M. L.; Döblinger, M.; Wang, K.; Hoye, R. L. Z.; Müller-Buschbaum, P.; Stranks, S. D.; Urban, A. S.; Polavarapu, L.; Feldmann, J. Boosting Tunable Blue Luminescence of Halide Perovskite Nanoplatelets through Postsynthetic Surface Trap Repair. *Nano Lett.* **2018**, *18*, 5231–5238.

(61) Zheng, Y.; Niu, T.; Ran, X.; Qiu, J.; Li, B.; Xia, Y.; Chen, Y.; Huang, W. Unique Characteristics of 2D Ruddlesden–Popper (2DRP) Perovskite for Future Photovoltaic Application. *J. Mater. Chem. A* **2019**, *7*, 13860–13872.

(62) Wang, F.; Bai, S.; Tress, W.; Hagfeldt, A.; Gao, F. Defects Engineering for High-Performance Perovskite Solar Cells. *npj Flex. Electron.* **2018**, *2*, 22.

(63) Uratani, H.; Yamashita, K. Charge Carrier Trapping at Surface Defects of Perovskite Solar Cell Absorbers: A First-Principles Study. *J. Phys. Chem. Lett.* **2017**, *8*, 742–746.

(64) Papavassiliou, G. C.; Pagona, G.; Karousis, N.; Mousdis, G. A.; Koutselas, I.; Vassilakopoulou, A. Nanocrystalline/Microcrystalline Materials Based on Lead–Halide Units. *J. Mater. Chem.* **2012**, *22*, 8271–8280.

(65) Papavassiliou, G. C.; Pagona, G.; Mousdis, G. A.; Karousis, N. Enhanced Phosphorescence from Nanocrystalline/Microcrystalline Materials Based on $(\text{CH}_3\text{NH}_3)(\text{1-naphthylmethyl ammonium})_2\text{Pb}_2\text{Cl}_7$ and Similar Compounds. *Chem. Phys. Lett.* **2013**, *570*, 80–84.

(66) Schmidt, L. C.; Pertegás, A.; González-Carrero, S.; Malinkiewicz, O.; Agouram, S.; Minguez Espallargas, G.; Bolink, H. J.; Galian, R. E.; Pérez-Prieto, J. Nontemplate Synthesis of $\text{CH}_3\text{NH}_3\text{PbBr}_3$ Perovskite Nanoparticles. *J. Am. Chem. Soc.* **2014**, *136*, 850–853.

(67) Talapin, D. V.; Mekis, I.; Götzinger, S.; Kornowski, A.; Benson, O.; Weller, H. CdSe/CdS/ZnS and CdSe/ZnSe/ZnS Core–Shell–Shell Nanocrystals. *J. Phys. Chem. B* **2004**, *108*, 18826–18831.

(68) Protesescu, L.; Yakunin, S.; Bodnarchuk, M. I.; Bertolotti, F.; Masciocchi, N.; Guagliardi, A.; Kovalenko, M. V. Monodisperse Formamidinium Lead Bromide Nanocrystals with Bright and Stable Green Photoluminescence. *J. Am. Chem. Soc.* **2016**, *138*, 14202–14205.

(69) Protesescu, L.; Yakunin, S.; Kumar, S.; Bär, J.; Bertolotti, F.; Masciocchi, N.; Guagliardi, A.; Grotevent, M.; Shorubalko, I.; Bodnarchuk, M. I.; Shih, C.-J.; Kovalenko, M. V. Dismantling the “Red Wall” of Colloidal Perovskites: Highly Luminescent Formamidinium and Formamidinium–Cesium Lead Iodide Nanocrystals. *ACS Nano* **2017**, *11*, 3119–3134.

(70) Hudait, B.; Dutta, S. K.; Pradhan, N. Isotropic CsPbBr_3 Perovskite Nanocrystals beyond Nanocubes: Growth and Optical Properties. *ACS Energy Lett.* **2020**, *5*, 650–656.

(71) Bera, S.; Behera, R. K.; Pradhan, N. α -Halo Ketone for Polyhedral Perovskite Nanocrystals: Evolutions, Shape Conversions, Ligand Chemistry, and Self-Assembly. *J. Am. Chem. Soc.* **2020**, *142*, 20865–20874.

(72) Peng, L.; Dutta, S. K.; Mondal, D.; Hudait, B.; Shyamal, S.; Xie, R.; Mahadevan, P.; Pradhan, N. Arm Growth and Facet Modulation in Perovskite Nanocrystals. *J. Am. Chem. Soc.* **2019**, *141*, 16160–16168.

(73) Tong, Y.; Fu, M.; Bladt, E.; Huang, H.; Richter, A. F.; Wang, K.; Müller-Buschbaum, P.; Bals, S.; Tamarat, P.; Lounis, B.; Feldmann, J.; Polavarapu, L. Chemical Cutting of Perovskite Nanowires into Single-Photon Emissive Low-Aspect-Ratio CsPbX_3 (X=Cl, Br, I) Nanorods. *Angew. Chem., Int. Ed.* **2018**, *57*, 16094–16098.

(74) Imran, M.; Di Stasio, F.; Dang, Z. Y.; Canale, C.; Khan, A. H.; Shamsi, J.; Brescia, R.; Prato, M.; Manna, L. Colloidal Synthesis of Strongly Fluorescent CsPbBr_3 Nanowires with Width Tunable down to the Quantum Confinement Regime. *Chem. Mater.* **2016**, *28*, 6450–6454.

(75) Zhang, D.; Eaton, S. W.; Yu, Y.; Dou, L.; Yang, P. Solution-Phase Synthesis of Cesium Lead Halide Perovskite Nanowires. *J. Am. Chem. Soc.* **2015**, *137*, 9230–9233.

(76) Zhang, D. D.; Yu, Y.; Bekenstein, Y.; Wong, A. B.; Alivisatos, A. P.; Yang, P. D. Ultrathin Colloidal Cesium Lead Halide Perovskite Nanowires. *J. Am. Chem. Soc.* **2016**, *138*, 13155–13158.

(77) Zhong, Q.; Cao, M.; Xu, Y.; Li, P.; Zhang, Y.; Hu, H.; Yang, D.; Xu, Y.; Wang, L.; Li, Y.; Zhang, X.; Zhang, Q. L-Type Ligand-Assisted Acid-Free Synthesis of CsPbBr_3 Nanocrystals with Near-Unity Photoluminescence Quantum Yield and High Stability. *Nano Lett.* **2019**, *19*, 4151–4157.

(78) Dutta, A.; Behera, R. K.; Pal, P.; Baitalik, S.; Pradhan, N. Near-Unity Photoluminescence Quantum Efficiency for All CsPbX_3 (X=Cl, Br, and I) Perovskite Nanocrystals: A Generic Synthesis Approach. *Angew. Chem., Int. Ed.* **2019**, *58*, 5552–5556.

(79) Dutta, A.; Dutta, S. K.; Das Adhikari, S.; Pradhan, N. Tuning the Size of CsPbBr_3 Nanocrystals: All at One Constant Temperature. *ACS Energy Lett.* **2018**, *3*, 329–334.

(80) Tong, Y.; Yao, E.-P.; Manzi, A.; Bladt, E.; Wang, K.; Döblinger, M.; Bals, S.; Müller-Buschbaum, P.; Urban, A. S.; Polavarapu, L.; Feldmann, J. Spontaneous Self-Assembly of Perovskite Nanocrystals into Electronically Coupled Supercrystals: Toward Filling the Green Gap. *Adv. Mater.* **2018**, *30*, 1801117.

(81) Rainò, G.; Becker, M. A.; Bodnarchuk, M. I.; Mahrt, R. F.; Kovalenko, M. V.; Stöferle, T. Superfluorescence from Lead Halide Perovskite Quantum Dot Superlattices. *Nature* **2018**, *563*, 671–675.

(82) Baranov, D.; Toso, S.; Imran, M.; Manna, L. Investigation into the Photoluminescence Red Shift in Cesium Lead Bromide Nanocrystal Superlattices. *J. Phys. Chem. Lett.* **2019**, *10*, 655–660.

(83) Baranov, D.; Fieramosca, A.; Yang, R. X.; Polimeno, L.; Lerario, G.; Toso, S.; Giansante, C.; Giorgi, M. D.; Tan, L. Z.; Sanvitto, D.; Manna, L. Aging of Self-Assembled Lead Halide Perovskite Nanocrystal Superlattices: Effects on Photoluminescence and Energy Transfer. *ACS Nano* **2021**, *15*, 650–664.

(84) De Roo, J.; Ibáñez, M.; Geiregat, P.; Nedelcu, G.; Walravens, W.; Maes, J.; Martins, J. C.; Van Driessche, I.; Kovalenko, M. V.; Hens, Z. Highly Dynamic Ligand Binding and Light Absorption Coefficient of Cesium Lead Bromide Perovskite Nanocrystals. *ACS Nano* **2016**, *10*, 2071–2081.

(85) Yang, D.; Li, X.; Zeng, H. Surface Chemistry of All Inorganic Halide Perovskite Nanocrystals: Passivation Mechanism and Stability. *Adv. Mater. Interfaces* **2018**, *5*, 1701662.

(86) Ye, J.; Byranvand, M. M.; Martínez, C. O.; Hoye, R. L.; Saliba, M.; Polavarapu, L. Defect Passivation in Lead–Halide Perovskite Nanocrystals and Thin Films: Toward Efficient LEDs and Solar Cells. *Angew. Chem., Int. Ed.* **2021**, DOI: 10.1002/anie.202102360.

(87) Behera, R. K.; Das Adhikari, S.; Dutta, S. K.; Dutta, A.; Pradhan, N. Blue-Emitting CsPbCl_3 Nanocrystals: Impact of Surface Passivation for Unprecedented Enhancement and Loss of Optical Emission. *J. Phys. Chem. Lett.* **2018**, *9*, 6884–6891.

(88) Koscher, B. A.; Swabeck, J. K.; Bronstein, N. D.; Alivisatos, A. P. Essentially Trap-Free CsPbBr_3 Colloidal Nanocrystals by Postsynthetic Thiocyanate Surface Treatment. *J. Am. Chem. Soc.* **2017**, *139*, 6566–6569.

(89) Chen, J.; Du, W.; Shi, J.; Li, M.; Wang, Y.; Zhang, Q.; Liu, X. Perovskite Quantum Dot Lasers. *InfoMat* **2020**, *2*, 170–183.

(90) Yuan, J.; Hazarika, A.; Zhao, Q.; Ling, X.; Moot, T.; Ma, W.; Luther, J. M. Metal Halide Perovskites in Quantum Dot Solar Cells: Progress and Prospects. *Joule* **2020**, *4*, 1160–1185.

(91) Wang, Y.; Yuan, J.; Zhang, X.; Ling, X.; Larson, B. W.; Zhao, Q.; Yang, Y.; Shi, Y.; Luther, J. M.; Ma, W. Surface Ligand Management Aided by a Secondary Amine Enables Increased Synthesis Yield of CsPbI_3 Perovskite Quantum Dots and High Photovoltaic Performance. *Adv. Mater.* **2020**, *32*, 2000449.

(92) Zhang, Y.; Liu, J.; Wang, Z.; Xue, Y.; Ou, Q.; Polavarapu, L.; Zheng, J.; Qi, X.; Bao, Q. Synthesis, Properties, and Optical

Applications of Low-Dimensional Perovskites. *Chem. Commun.* **2016**, *52*, 13637–13655.

(93) Liu, X.; Yu, D.; Song, X.; Zeng, H. Metal Halide Perovskites: Synthesis, Ion Migration, and Application in Field-Effect Transistors. *Small* **2018**, *14*, 1801460.

(94) Chang, S.; Bai, Z.; Zhong, H. *In Situ* Fabricated Perovskite Nanocrystals: A Revolution in Optical Materials. *Adv. Opt. Mater.* **2018**, *6*, 1800380.

(95) Park, B.-W.; Philippe, B.; Zhang, X.; Rensmo, H.; Boschloo, G.; Johansson, E. M. J. Bismuth Based Hybrid Perovskites $A_3Bi_2I_9$ (A: Methylammonium or Cesium) for Solar Cell Application. *Adv. Mater.* **2015**, *27*, 6806–6813.

(96) Rieger, S.; Bohn, B. J.; Döblinger, M.; Richter, A. F.; Tong, Y.; Wang, K.; Müller-Buschbaum, P.; Polavarapu, L.; Leppert, L.; Stolarczyk, J. K.; Feldmann, J. Excitons and Narrow Bands Determine the Optical Properties of Cesium Bismuth Halides. *Phys. Rev. B: Condens. Matter Mater. Phys.* **2019**, *100*, 201404.

(97) Correa-Baena, J.-P.; Nienhaus, L.; Kurchin, R. C.; Shin, S. S.; Wieghold, S.; Putri Hartono, N. T.; Layurova, M.; Klein, N. D.; Poindexter, J. R.; Polizzotti, A.; Sun, S.; Bawendi, M. G.; Buonassisi, T. A-Site Cation in Inorganic $A_3Sb_2I_9$ Perovskite Influences Structural Dimensionality, Exciton Binding Energy, and Solar Cell Performance. *Chem. Mater.* **2018**, *30*, 3734–3742.

(98) Huang, H.; Bodnarchuk, M. I.; Kershaw, S. V.; Kovalenko, M. V.; Rogach, A. L. Lead Halide Perovskite Nanocrystals in the Research Spotlight: Stability and Defect Tolerance. *ACS Energy Lett.* **2017**, *2*, 2071–2083.

(99) Polavarapu, L.; Zhang, Q.; Krahne, R. Nanoscale & Nanoscale Advances Joint Themed Collection on Halide Perovskite Nanocrystals. *Nanoscale* **2019**, *11*, 8648–8650.

(100) Saidaminov, M. I.; Mohammed, O. F.; Bakr, O. M. Low-Dimensional-Networked Metal Halide Perovskites: The Next Big Thing. *ACS Energy Lett.* **2017**, *2*, 889–896.

(101) Seth, S.; Ahmed, T.; De, A.; Samanta, A. Tackling the Defects, Stability, and Photoluminescence of $CsPbX_3$ Perovskite Nanocrystals. *ACS Energy Lett.* **2019**, *4*, 1610–1618.

(102) Swarnkar, A.; Ravi, V. K.; Nag, A. Beyond Colloidal Cesium Lead Halide Perovskite Nanocrystals: Analogous Metal Halides and Doping. *ACS Energy Lett.* **2017**, *2*, 1089–1098.

(103) Wu, Y.; Li, X.; Zeng, H. Highly Luminescent and Stable Halide Perovskite Nanocrystals. *ACS Energy Lett.* **2019**, *4*, 673–681.

(104) Bera, S.; Pradhan, N. Perovskite Nanocrystal Heterostructures: Synthesis, Optical Properties, and Applications. *ACS Energy Lett.* **2020**, *5*, 2858–2872.

(105) He, X.; Qiu, Y.; Yang, S. Fully-Inorganic Trihalide Perovskite Nanocrystals: A New Research Frontier of Optoelectronic Materials. *Adv. Mater.* **2017**, *29*, 1700775.

(106) Huang, J.; Lai, M.; Lin, J.; Yang, P. Rich Chemistry in Inorganic Halide Perovskite Nanostructures. *Adv. Mater.* **2018**, *30*, 1802856.

(107) Jeong, B.; Han, H.; Park, C. Micro- and Nanopatterning of Halide Perovskites Where Crystal Engineering for Emerging Photoelectronics Meets Integrated Device Array Technology. *Adv. Mater.* **2020**, *32*, 2000597.

(108) Zhang, X.; Li, L.; Sun, Z.; Luo, J. Rational Chemical Doping of Metal Halide Perovskites. *Chem. Soc. Rev.* **2019**, *48*, 517–539.

(109) Ghosh, S.; Pradhan, B. Lead-Free Metal Halide Perovskite Nanocrystals: Challenges, Applications, and Future Aspects. *Chem-NanoMat* **2019**, *5*, 300–312.

(110) Luo, B.; Naghadeh, S. B.; Zhang, J. Z. Lead Halide Perovskite Nanocrystals: Stability, Surface Passivation, and Structural Control. *Chem-NanoMat* **2017**, *3*, 456–465.

(111) Kovalenko, M. V.; Bodnarchuk, M. I. Lead Halide Perovskite Nanocrystals: From Discovery to Self-Assembly and Applications. *Chimia* **2017**, *71*, 461–470.

(112) Yan, F.; Tan, S. T.; Li, X.; Demir, H. V. Light Generation in Lead Halide Perovskite Nanocrystals: LEDs, Color Converters, Lasers, and Other Applications. *Small* **2019**, *15*, 1902079.

(113) Dong, Y.; Zhao, Y.; Zhang, S.; Dai, Y.; Liu, L.; Li, Y.; Chen, Q. Recent Advances Toward Practical Use of Halide Perovskite Nanocrystals. *J. Mater. Chem. A* **2018**, *6*, 21729–21746.

(114) Ravi, V. K.; Singhal, N.; Nag, A. Initiation and Future Prospects of Colloidal Metal Halide Double-Perovskite Nanocrystals: Cs_2AgBiX_6 (X = Cl, Br, I). *J. Mater. Chem. A* **2018**, *6*, 21666–21675.

(115) Que, M.; Zhu, L.; Guo, Y.; Que, W.; Yun, S. Toward Perovskite Nanocrystalline Solar Cells: Progress and Potential. *J. Mater. Chem. C* **2020**, *8*, 5321–5334.

(116) Kaur, G.; Ghosh, H. N. Hot Carrier Relaxation in $CsPbBr_3$ -Based Perovskites: A Polaron Perspective. *J. Phys. Chem. Lett.* **2020**, *11*, 8765–8776.

(117) Zhang, Q.; Yin, Y. All-Inorganic Metal Halide Perovskite Nanocrystals: Opportunities and Challenges. *ACS Cent. Sci.* **2018**, *4*, 668–679.

(118) Li, Z.; Peng, X. Size/Shape-Controlled Synthesis of Colloidal CdSe Quantum Disks: Ligand and Temperature Effects. *J. Am. Chem. Soc.* **2011**, *133*, 6578–6586.

(119) Brus, L. Electronic Wave Functions in Semiconductor Clusters: Experiment and Theory. *J. Phys. Chem.* **1986**, *90*, 2555–2560.

(120) Brus, L. E. A Simple Model for the Ionization Potential, Electron Affinity, and Aqueous Redox Potentials of Small Semiconductor Crystallites. *J. Chem. Phys.* **1983**, *79*, 5566–5571.

(121) Murphy, J. E.; Beard, M. C.; Norman, A. G.; Ahrenkiel, S. P.; Johnson, J. C.; Yu, P.; Mićić, O. I.; Ellingson, R. J.; Nozik, A. J. PbTe Colloidal Nanocrystals: Synthesis, Characterization, and Multiple Exciton Generation. *J. Am. Chem. Soc.* **2006**, *128*, 3241–3247.

(122) Talapin, D. V.; Rogach, A. L.; Kornowski, A.; Haase, M.; Weller, H. Highly Luminescent Monodisperse CdSe and CdSe/ZnS Nanocrystals Synthesized in a Hexadecylamine-Trioctylphosphine Oxide-Trioctylphosphine Mixture. *Nano Lett.* **2001**, *1*, 207–211.

(123) Steigerwald, M. L.; Brus, L. E. Semiconductor Crystallites: A Class of Large Molecules. *Acc. Chem. Res.* **1990**, *23*, 183–188.

(124) Gao, M.-R.; Xu, Y.-F.; Jiang, J.; Yu, S.-H. Nanostructured Metal Chalcogenides: Synthesis, Modification, and Applications in Energy Conversion and Storage Devices. *Chem. Soc. Rev.* **2013**, *42*, 2986–3017.

(125) Nikl, M.; Nitsch, K.; Polák, K.; Mihókova, E.; Zazubovich, S.; Pazzi, G. P.; Fabeni, P.; Salvini, L.; Aceves, R.; Barbosa-Flores, M.; Salas, R. P.; Gurioli, M.; Scacco, A. Quantum Size Effect in the Excitonic Luminescence of $CsPbX_3$ -Like Quantum Dots in CsX (X = Cl, Br) Single Crystal Host. *J. Lumin.* **1997**, *72-74*, 377–379.

(126) Nikl, M.; Nitsch, K.; Polák, K.; Pazzi, G. P.; Fabeni, P.; Citrin, D. S.; Gurioli, M. Optical Properties of the Pb^{2+} -Based Aggregated Phase in a CsCl Host Crystal: Quantum-Confinement Effects. *Phys. Rev. B: Condens. Matter Mater. Phys.* **1995**, *51*, 5192–5199.

(127) Ishihara, T.; Takahashi, J.; Goto, T. Optical Properties Due to Electronic Transitions in Two-Dimensional Semiconductors $(C_nH_{2n+1}NH_3)_2PbI_4$. *Phys. Rev. B: Condens. Matter Mater. Phys.* **1990**, *42*, 11099–11107.

(128) Koutselas, I. B.; Ducasse, L.; Papavassiliou, G. C. Electronic Properties of Three- and Low-Dimensional Semiconducting Materials with Pb Halide and Sn Halide Units. *J. Phys.: Condens. Matter* **1996**, *8*, 1217–1227.

(129) Im, J.-H.; Lee, C.-R.; Lee, J.-W.; Park, S.-W.; Park, N.-G. 6.5% Efficient Perovskite Quantum-Dot-Sensitized Solar Cell. *Nanoscale* **2011**, *3*, 4088–4093.

(130) Ishihara, T.; Takahashi, J.; Goto, T. Exciton State in Two-Dimensional Perovskite Semiconductor $(C_{10}H_{21}NH_3)_2PbI_4$. *Solid State Commun.* **1989**, *69*, 933–936.

(131) Protesescu, L.; Yakunin, S.; Nazarenko, O.; Dirin, D. N.; Kovalenko, M. V. Low-Cost Synthesis of Highly Luminescent Colloidal Lead Halide Perovskite Nanocrystals by Wet Ball Milling. *ACS Appl. Nano Mater.* **2018**, *1*, 1300–1308.

(132) Hintermayr, V. A.; Richter, A. F.; Ehrat, F.; Döblinger, M.; Vanderlinden, W.; Sichert, J. A.; Tong, Y.; Polavarapu, L.; Feldmann, J.; Urban, A. S. Tuning the Optical Properties of Perovskite

Nanoplatelets through Composition and Thickness by Ligand-Assisted Exfoliation. *Adv. Mater.* **2016**, *28*, 9478–9485.

(133) Pan, Q.; Hu, H.; Zou, Y.; Chen, M.; Wu, L.; Yang, D.; Yuan, X.; Fan, J.; Sun, B.; Zhang, Q. Microwave-Assisted Synthesis of High-Quality “All-Inorganic” CsPbX_3 ($X = \text{Cl}, \text{Br}, \text{I}$) Perovskite Nanocrystals and their Application in Light Emitting Diodes. *J. Mater. Chem. C* **2017**, *5*, 10947–10954.

(134) Chen, M.; Zou, Y.; Wu, L.; Pan, Q.; Yang, D.; Hu, H.; Tan, Y.; Zhong, Q.; Xu, Y.; Liu, H.; Sun, B.; Zhang, Q. Solvothermal Synthesis of High-Quality All-Inorganic Cesium Lead Halide Perovskite Nanocrystals: From Nanocube to Ultrathin Nanowire. *Adv. Funct. Mater.* **2017**, *27*, 1701121.

(135) Debuigne, F.; Jeunieau, L.; Wiame, M.; B. Nagy, J. Synthesis of Organic Nanoparticles in Different W/O Microemulsions. *Langmuir* **2000**, *16*, 7605–7611.

(136) Fu, H.-B.; Yao, J.-N. Size Effects on the Optical Properties of Organic Nanoparticles. *J. Am. Chem. Soc.* **2001**, *123*, 1434–1439.

(137) Horn, D.; Rieger, J. Organic Nanoparticles in the Aqueous Phase—Theory, Experiment, and Use. *Angew. Chem., Int. Ed.* **2001**, *40*, 4330–4361.

(138) Huang, H.; Susha, A. S.; Kershaw, S. V.; Hung, T. F.; Rogach, A. L. Control of Emission Color of High Quantum Yield $\text{CH}_3\text{NH}_3\text{PbBr}_3$ Perovskite Quantum Dots by Precipitation Temperature. *Adv. Sci.* **2015**, *2*, 1500194.

(139) Dang, Z.; Shamsi, J.; Palazon, F.; Imran, M.; Akkerman, Q. A.; Park, S.; Bertoni, G.; Prato, M.; Brescia, R.; Manna, L. *In Situ* Transmission Electron Microscopy Study of Electron Beam-Induced Transformations in Colloidal Cesium Lead Halide Perovskite Nanocrystals. *ACS Nano* **2017**, *11*, 2124–2132.

(140) Li, Y.-F.; Chou, S.-Y.; Huang, P.; Xiao, C.; Liu, X.; Xie, Y.; Zhao, F.; Huang, Y.; Feng, J.; Zhong, H.; Sun, H.-B.; Pei, Q. Stretchable Organometal-Halide-Perovskite Quantum-Dot Light-Emitting Diodes. *Adv. Mater.* **2019**, *31*, 1807516.

(141) Huang, H.; Zhao, F.; Liu, L.; Zhang, F.; Wu, X.-g.; Shi, L.; Zou, B.; Pei, Q.; Zhong, H. Emulsion Synthesis of Size-Tunable $\text{CH}_3\text{NH}_3\text{PbBr}_3$ Quantum Dots: An Alternative Route toward Efficient Light-Emitting Diodes. *ACS Appl. Mater. Interfaces* **2015**, *7*, 28128–28133.

(142) Lu, M.; Zhang, Y.; Wang, S.; Guo, J.; Yu, W. W.; Rogach, A. L. Metal Halide Perovskite Light-Emitting Devices: Promising Technology for Next-Generation Displays. *Adv. Funct. Mater.* **2019**, *29*, 1902008.

(143) Imran, M.; Ijaz, P.; Baranov, D.; Goldoni, L.; Petralanda, U.; Akkerman, Q.; Abdelhady, A. L.; Prato, M.; Bianchini, P.; Infante, I.; Manna, L. Shape-Pure, Nearly Monodispersed CsPbBr_3 Nanocubes Prepared Using Secondary Aliphatic Amines. *Nano Lett.* **2018**, *18*, 7822–7831.

(144) Lignos, I.; Stavrakis, S.; Nedelcu, G.; Protesescu, L.; deMello, A. J.; Kovalenko, M. V. Synthesis of Cesium Lead Halide Perovskite Nanocrystals in a Droplet-Based Microfluidic Platform: Fast Parametric Space Mapping. *Nano Lett.* **2016**, *16*, 1869–1877.

(145) Almeida, G.; Goldoni, L.; Akkerman, Q.; Dang, Z.; Khan, A. H.; Marras, S.; Moreels, I.; Manna, L. Role of Acid-Base Equilibria in the Size, Shape, and Phase Control of Cesium Lead Bromide Nanocrystals. *ACS Nano* **2018**, *12*, 1704–1711.

(146) Cottingham, P.; Brutchev, R. L. On the Crystal Structure of Colloidally Prepared CsPbBr_3 Quantum Dots. *Chem. Commun.* **2016**, *52*, 5246–5249.

(147) Becker, M. A.; Vaxenburg, R.; Nedelcu, G.; Sercel, P. C.; Shabaev, A.; Mehl, M. J.; Michopoulos, J. G.; Lambrakos, S. G.; Bernstein, N.; Lyons, J. L.; Stöferle, T.; Mahrt, R. F.; Kovalenko, M. V.; Norris, D. J.; Rainò, G.; Efros, A. L. Bright Triplet Excitons in Caesium Lead Halide Perovskites. *Nature* **2018**, *553*, 189–193.

(148) Mondal, N.; De, A.; Samanta, A. Achieving Near-Unity Photoluminescence Efficiency for Blue-Violet-Emitting Perovskite Nanocrystals. *ACS Energy Lett.* **2019**, *4*, 32–39.

(149) Dong, Y.; Qiao, T.; Kim, D.; Parobek, D.; Rossi, D.; Son, D. H. Precise Control of Quantum Confinement in Cesium Lead Halide Perovskite Quantum Dots *via* Thermodynamic Equilibrium. *Nano Lett.* **2018**, *18*, 3716–3722.

(150) Rossi, D.; Wang, H.; Dong, Y.; Qiao, T.; Qian, X.; Son, D. H. Light-Induced Activation of Forbidden Exciton Transition in Strongly Confined Perovskite Quantum Dots. *ACS Nano* **2018**, *12*, 12436–12443.

(151) Cheng, O. H.-C.; Qiao, T.; Sheldon, M.; Son, D. H. Size- and Temperature-Dependent Photoluminescence Spectra of Strongly Confined CsPbBr_3 Quantum Dots. *Nanoscale* **2020**, *12*, 13113–13118.

(152) Li, Y.; Luo, X.; Liu, Y.; Lu, X.; Wu, K. Size- and Composition-Dependent Exciton Spin Relaxation in Lead Halide Perovskite Quantum Dots. *ACS Energy Lett.* **2020**, *5*, 1701–1708.

(153) Rossi, D.; Liu, X.; Lee, Y.; Khurana, M.; Puthenpurayil, J.; Kim, K.; Akimov, A. V.; Cheon, J.; Son, D. H. Intense Dark Exciton Emission from Strongly Quantum Confined CsPbBr_3 Nanocrystals. *Nano Lett.* **2020**, *20*, 7321–7326.

(154) Forde, A.; Fagan, J. A.; Schaller, R. D.; Thomas, S. A.; Brown, S. L.; Kurtti, M. B.; Petersen, R. J.; Kilin, D. S.; Hobbs, E. K. Brightly Luminescent CsPbBr_3 Nanocrystals through Ultracentrifugation. *J. Phys. Chem. Lett.* **2020**, *11*, 7133–7140.

(155) Li, Y.; Huang, H.; Xiong, Y.; Richter, A. F.; Kershaw, S. V.; Feldmann, J.; Rogach, A. L. Using Polar Alcohols for the Direct Synthesis of Cesium Lead Halide Perovskite Nanorods with Anisotropic Emission. *ACS Nano* **2019**, *13*, 8237–8245.

(156) Zhai, W.; Lin, J.; Li, Q.; Zheng, K.; Huang, Y.; Yao, Y.; He, X.; Li, L.; Yu, C.; Liu, C.; Fang, Y.; Liu, Z.; Tang, C. Solvothermal Synthesis of Ultrathin Cesium Lead Halide Perovskite Nanoplatelets with Tunable Lateral Sizes and Their Reversible Transformation into Cs_4PbBr_6 Nanocrystals. *Chem. Mater.* **2018**, *30*, 3714–3721.

(157) Ahmed, G. H.; Yin, J.; Bose, R.; Sinatra, L.; Alarousu, E.; Yengel, E.; AlYami, N. M.; Saidaminov, M. I.; Zhang, Y.; Hedhili, M. N.; Bakr, O. M.; Brédas, J.-L.; Mohammed, O. F. Pyridine-Induced Dimensionality Change in Hybrid Perovskite Nanocrystals. *Chem. Mater.* **2017**, *29*, 4393–4400.

(158) Vybornyi, O.; Yakunin, S.; Kovalenko, M. V. Polar-Solvent-Free Colloidal Synthesis of Highly Luminescent Alkylammonium Lead Halide Perovskite Nanocrystals. *Nanoscale* **2016**, *8*, 6278–6283.

(159) Levchuk, I.; Osvet, A.; Tang, X.; Brandl, M.; Perea, J. D.; Hoegl, F.; Matt, G. J.; Hock, R.; Batentschuk, M.; Brabec, C. J. Brightly Luminescent and Color-Tunable Formamidinium Lead Halide Perovskite FAPbX_3 ($X = \text{Cl}, \text{Br}, \text{I}$) Colloidal Nanocrystals. *Nano Lett.* **2017**, *17*, 2765–2770.

(160) Zhang, Y.; Thomas, C. J.; Guillaussier, A.; Smilgies, D.-M.; Korgel, B. A. Thermal Phase Transitions in Superlattice Assemblies of Cuboidal $\text{CH}_3\text{NH}_3\text{PbI}_3$ Nanocrystals Followed by Grazing Incidence X-ray Scattering. *J. Phys. Chem. C* **2019**, *123*, 17555–17565.

(161) Imran, M.; Ijaz, P.; Goldoni, L.; Maggioni, D.; Petralanda, U.; Prato, M.; Almeida, G.; Infante, I.; Manna, L. Simultaneous Cationic and Anionic Ligand Exchange For Colloidally Stable CsPbBr_3 Nanocrystals. *ACS Energy Lett.* **2019**, *4*, 819–824.

(162) Li, Y.; Ding, T.; Luo, X.; Tian, Y.; Lu, X.; Wu, K. Synthesis and Spectroscopy of Monodispersed, Quantum-Confining FAPbBr_3 Perovskite Nanocrystals. *Chem. Mater.* **2020**, *32*, 549–556.

(163) Minh, D. N.; Kim, J.; Hyon, J.; Sim, J. H.; Sowlil, H. H.; Seo, C.; Nam, J.; Eom, S.; Suk, S.; Lee, S.; Kim, E.; Kang, Y. Room-Temperature Synthesis of Widely Tunable Formamidinium Lead Halide Perovskite Nanocrystals. *Chem. Mater.* **2017**, *29*, 5713–5719.

(164) Zu, Y.; Xi, J.; Li, L.; Dai, J.; Wang, S.; Yun, F.; Jiao, B.; Dong, H.; Hou, X.; Wu, Z. High-Brightness and Color-Tunable FAPbBr_3 Perovskite Nanocrystals 2.0 Enable Ultrapure Green Luminescence for Achieving Recommendation 2020 Displays. *ACS Appl. Mater. Interfaces* **2020**, *12*, 2835–2841.

(165) Koczkur, K. M.; Moudikoudis, S.; Polavarapu, L.; Skrabalak, S. E. Polyvinylpyrrolidone (PVP) in Nanoparticle Synthesis. *Dalton Trans.* **2015**, *44*, 17883–17905.

(166) Ling, D.; Hackett, M. J.; Hyeon, T. Surface Ligands in Synthesis, Modification, Assembly and Biomedical Applications of Nanoparticles. *Nano Today* **2014**, *9*, 457–477.

(167) Zhang, B.; Goldoni, L.; Lambruschini, C.; Moni, L.; Imran, M.; Pianetti, A.; Pinchetti, V.; Brovelli, S.; De Trizio, L.; Manna, L. Stable and Size Tunable CsPbBr_3 Nanocrystals Synthesized with Oleylphosphonic Acid. *Nano Lett.* **2020**, *20*, 8847–8853.

(168) Cai, Y.; Wang, H.; Li, Y.; Wang, L.; Lv, Y.; Yang, X.; Xie, R.-J. Trimethylsilyl Iodine-Mediated Synthesis of Highly Bright Red-Emitting CsPbI_3 Perovskite Quantum Dots with Significantly Improved Stability. *Chem. Mater.* **2019**, *31*, 881–889.

(169) Wu, L.; Zhong, Q.; Yang, D.; Chen, M.; Hu, H.; Pan, Q.; Liu, H.; Cao, M.; Xu, Y.; Sun, B.; Zhang, Q. Improving the Stability and Size Tunability of Cesium Lead Halide Perovskite Nanocrystals Using Trioctylphosphine Oxide as the Capping Ligand. *Langmuir* **2017**, *33*, 12689–12696.

(170) Krieg, F.; Ong, Q. K.; Burian, M.; Rainò, G.; Naumenko, D.; Amenitsch, H.; Süess, A.; Grotevent, M. J.; Krumeich, F.; Bodnarchuk, M. I.; Shorubalko, I.; Stellacci, F.; Kovalenko, M. V. Stable Ultraconcentrated and Ultradilute Colloids of CsPbX_3 ($X = \text{Cl}, \text{Br}$) Nanocrystals Using Natural Lecithin as a Capping Ligand. *J. Am. Chem. Soc.* **2019**, *141*, 19839–19849.

(171) Krieg, F.; Ochsenbein, S. T.; Yakunin, S.; ten Brinck, S.; Aellen, P.; Süess, A.; Clerc, B.; Guggisberg, D.; Nazarenko, O.; Shynkarenko, Y.; Kumar, S.; Shih, C.-J.; Infante, I.; Kovalenko, M. V. Colloidal CsPbX_3 ($X = \text{Cl}, \text{Br}, \text{I}$) Nanocrystals 2.0: Zwitterionic Capping Ligands for Improved Durability and Stability. *ACS Energy Lett.* **2018**, *3*, 641–646.

(172) Pan, J.; Shang, Y.; Yin, J.; De Bastiani, M.; Peng, W.; Dursun, I.; Sinatra, L.; El-Zohry, A. M.; Hedhili, M. N.; Emwas, A.-H.; Mohammed, O. F.; Ning, Z.; Bakr, O. M. Bidentate Ligand-Passivated CsPbI_3 Perovskite Nanocrystals for Stable Near-Unity Photoluminescence Quantum Yield and Efficient Red Light-Emitting Diodes. *J. Am. Chem. Soc.* **2018**, *140*, 562–565.

(173) Wang, S.; Du, L.; Jin, Z.; Xin, Y.; Matoussi, H. Enhanced Stabilization and Easy Phase Transfer of CsPbBr_3 Perovskite Quantum Dots Promoted by High-Affinity Polyzwitterionic Ligands. *J. Am. Chem. Soc.* **2020**, *142*, 12669–12680.

(174) Yoo, D.; Woo, J. Y.; Kim, Y.; Kim, S. W.; Wei, S.-H.; Jeong, S.; Kim, Y.-H. Origin of the Stability and Transition from Anionic to Cationic Surface Ligand Passivation of All-Inorganic Cesium Lead Halide Perovskite Nanocrystals. *J. Phys. Chem. Lett.* **2020**, *11*, 652–658.

(175) Liu, F.; Zhang, Y.; Ding, C.; Kobayashi, S.; Izuishi, T.; Nakazawa, N.; Toyoda, T.; Ohta, T.; Hayase, S.; Minemoto, T.; Yoshino, K.; Dai, S.; Shen, Q. Highly Luminescent Phase-Stable CsPbI_3 Perovskite Quantum Dots Achieving Near 100% Absolute Photoluminescence Quantum Yield. *ACS Nano* **2017**, *11*, 10373–10383.

(176) Sun, S.; Yuan, D.; Xu, Y.; Wang, A.; Deng, Z. Ligand-Mediated Synthesis of Shape-Controlled Cesium Lead Halide Perovskite Nanocrystals via Reprecipitation Process at Room Temperature. *ACS Nano* **2016**, *10*, 3648–3657.

(177) Pan, A.; He, B.; Fan, X.; Liu, Z.; Urban, J. J.; Alivisatos, A. P.; He, L.; Liu, Y. Insight into the Ligand-Mediated Synthesis of Colloidal CsPbBr_3 Perovskite Nanocrystals: The Role of Organic Acid, Base, and Cesium Precursors. *ACS Nano* **2016**, *10*, 7943–7954.

(178) Imran, M.; Caligiuri, V.; Wang, M.; Goldoni, L.; Prato, M.; Krahne, R.; De Trizio, L.; Manna, L. Benzoyl Halides as Alternative Precursors for the Colloidal Synthesis of Lead-Based Halide Perovskite Nanocrystals. *J. Am. Chem. Soc.* **2018**, *140*, 2656–2664.

(179) Almeida, G.; Ashton, O. J.; Goldoni, L.; Maggioni, D.; Petralanda, U.; Mishra, N.; Akkerman, Q. A.; Infante, I.; Snaith, H. J.; Manna, L. The Phosphine Oxide Route toward Lead Halide Perovskite Nanocrystals. *J. Am. Chem. Soc.* **2018**, *140*, 14878–14886.

(180) Ashton, O. J.; Marshall, A. R.; Warby, J. H.; Wenger, B.; Snaith, H. J. A Phosphine Oxide Route to Formamidinium Lead Tribromide Nanoparticles. *Chem. Mater.* **2020**, *32*, 7172–7180.

(181) Akkerman, Q. A.; Martínez-Sarti, L.; Goldoni, L.; Imran, M.; Baranov, D.; Bolink, H. J.; Palazon, F.; Manna, L. Molecular Iodine for a General Synthesis of Binary and Ternary Inorganic and Hybrid Organic–Inorganic Iodide Nanocrystals. *Chem. Mater.* **2018**, *30*, 6915–6921.

(182) Paul, S.; Samanta, A. N-Bromosuccinimide as Bromide Precursor for Direct Synthesis of Stable and Highly Luminescent Green-Emitting Perovskite Nanocrystals. *ACS Energy Lett.* **2020**, *5*, 64–69.

(183) Creutz, S. E.; Crites, E. N.; De Siena, M. C.; Gamelin, D. R. Colloidal Nanocrystals of Lead-Free Double-Perovskite (Elpasolite) Semiconductors: Synthesis and Anion Exchange To Access New Materials. *Nano Lett.* **2018**, *18*, 1118–1123.

(184) Li, J.; Xu, L.; Wang, T.; Song, J.; Chen, J.; Xue, J.; Dong, Y.; Cai, B.; Shan, Q.; Han, B.; Zeng, H. 50-Fold EQE Improvement Upto 6.27% of Solution-Processed All-Inorganic Perovskite CsPbBr_3 QLEDs via Surface Ligand Density Control. *Adv. Mater.* **2017**, *29* (5), 1603885.

(185) Swarnkar, A.; Marshall, A. R.; Sanehira, E. M.; Chernomordik, B. D.; Moore, D. T.; Christians, J. A.; Chakrabarti, T.; Luther, J. M. Quantum Dot-Induced Phase Stabilization of $\alpha\text{-CsPbI}_3$ Perovskite for High-Efficiency Photovoltaics. *Science* **2016**, *354*, 92–95.

(186) Sun, J. K.; Huang, S.; Liu, X. Z.; Xu, Q.; Zhang, Q. H.; Jiang, W. J.; Xue, D. J.; Xu, J. C.; Ma, J. Y.; Ding, J.; Ge, Q. Q.; Gu, L.; Fang, X. H.; Zhong, H. Z.; Hu, J. S.; Wan, L. J. Polar Solvent Induced Lattice Distortion of Cubic CsPbI_3 Nanocubes and Hierarchical Self-Assembly into Orthorhombic Single-Crystalline Nanowires. *J. Am. Chem. Soc.* **2018**, *140*, 11705–11715.

(187) Zhang, Y.; Siegler, T. D.; Thomas, C. J.; Abney, M. K.; Shah, T.; De Gorostiza, A.; Greene, R. M.; Korgel, B. A. A “Tips and Tricks” Practical Guide to the Synthesis of Metal Halide Perovskite Nanocrystals. *Chem. Mater.* **2020**, *32*, 5410–5423.

(188) Wang, L.; Williams, N. E.; Malachosky, E. W.; Otto, J. P.; Hayes, D.; Wood, R. E.; Guyot-Sionnest, P.; Engel, G. S. Scalable Ligand-Mediated Transport Synthesis of Organic–Inorganic Hybrid Perovskite Nanocrystals with Resolved Electronic Structure and Ultrafast Dynamics. *ACS Nano* **2017**, *11*, 2689–2696.

(189) Jiang, Y.; Qin, C.; Cui, M.; He, T.; Liu, K.; Huang, Y.; Luo, M.; Zhang, L.; Xu, H.; Li, S.; Wei, J.; Liu, Z.; Wang, H.; Kim, G.-H.; Yuan, M.; Chen, J. Spectra Stable Blue Perovskite Light-Emitting Diodes. *Nat. Commun.* **2019**, *10*, 1868.

(190) Chiba, T.; Hoshi, K.; Pu, Y.-J.; Takeda, Y.; Hayashi, Y.; Ohisa, S.; Kawata, S.; Kido, J. High-Efficiency Perovskite Quantum-Dot Light-Emitting Devices by Effective Washing Process and Interfacial Energy Level Alignment. *ACS Appl. Mater. Interfaces* **2017**, *9*, 18054–18060.

(191) Thomas, C. J.; Zhang, Y.; Guillaussier, A.; Bdeir, K.; Aly, O. F.; Kim, H. G.; Noh, J.; Reimnitz, L. C.; Li, J.; Deepak, F. L.; Smilgies, D.-M.; Milliron, D. J.; Korgel, B. A. Thermal Stability of the Black Perovskite Phase in Cesium Lead Iodide Nanocrystals Under Humid Conditions. *Chem. Mater.* **2019**, *31*, 9750–9758.

(192) Suri, M.; Hazarika, A.; Larson, B. W.; Zhao, Q.; Vallés-Pelarda, M.; Siegler, T. D.; Abney, M. K.; Ferguson, A. J.; Korgel, B. A.; Luther, J. M. Enhanced Open-Circuit Voltage of Wide-Bandgap Perovskite Photovoltaics by Using Alloyed $(\text{FA}_{1-x}\text{Cs}_x)\text{Pb}(\text{I}_{1-x}\text{Br}_x)$ Quantum Dots. *ACS Energy Lett.* **2019**, *4*, 1954–1960.

(193) Zhang, Y.; Shah, T.; Deepak, F. L.; Korgel, B. A. Surface Science and Colloidal Stability of Double-Perovskite $\text{Cs}_2\text{AgBiBr}_6$ Nanocrystals and Their Superlattices. *Chem. Mater.* **2019**, *31*, 7962–7969.

(194) Nenon, D. P.; Pressler, K.; Kang, J.; Koscher, B. A.; Olshansky, J. H.; Osowiecki, W. T.; Koc, M. A.; Wang, L.-W.; Alivisatos, A. P. Design Principles for Trap-Free CsPbX_3 Nanocrystals: Enumerating and Eliminating Surface Halide Vacancies with Softer Lewis Bases. *J. Am. Chem. Soc.* **2018**, *140*, 17760–17772.

(195) Bodnarchuk, M. I.; Boehme, S. C.; ten Brinck, S.; Bernasconi, C.; Shynkarenko, Y.; Krieg, F.; Widmer, R.; Aeschlimann, B.; Günther, D.; Kovalenko, M. V.; Infante, I. Rationalizing and Controlling the Surface Structure and Electronic Passivation of Cesium Lead Halide Nanocrystals. *ACS Energy Lett.* **2019**, *4*, 63–74.

(196) Bekenstein, Y.; Dahl, J. C.; Huang, J.; Osowiecki, W. T.; Swabeck, J. K.; Chan, E. M.; Yang, P.; Alivisatos, A. P. The Making

and Breaking of Lead-Free Double Perovskite Nanocrystals of Cesium Silver–Bismuth Halide Compositions. *Nano Lett.* **2018**, *18*, 3502–3508.

(197) Fan, Q.; Biesold-McGee, G. V.; Ma, J.; Xu, Q.; Pan, S.; Peng, J.; Lin, Z. Lead-Free Halide Perovskite Nanocrystals: Crystal Structures, Synthesis, Stabilities, and Optical Properties. *Angew. Chem., Int. Ed.* **2020**, *59*, 1030–1046.

(198) Mitzi, D. B. Synthesis, Structure, and Properties of Organic-Inorganic Perovskites and Related Materials. *Prog. Inorg. Chem.* **2007**, *48*, 1–121.

(199) Mitzi, D. B.; Wang, S.; Feild, C. A.; Chess, C. A.; Guloy, A. M. Conducting Layered Organic-Inorganic Halides Containing (110)-Oriented Perovskite Sheets. *Science* **1995**, *267*, 1473–1476.

(200) Ishihara, T.; Hong, X.; Ding, J.; Nurmikko, A. V. Dielectric Confinement Effect For Exciton and Biexciton States in PbI_4 -Based 2-Dimensional Semiconductor Structures. *Surf. Sci.* **1992**, *267*, 323–326.

(201) Stoumpos, C. C.; Cao, D. H.; Clark, D. J.; Young, J.; Rondinelli, J. M.; Jang, J. I.; Hupp, J. T.; Kanatzidis, M. G. Ruddlesden–Popper Hybrid Lead Iodide Perovskite 2D Homologous Semiconductors. *Chem. Mater.* **2016**, *28*, 2852–2867.

(202) Nagabhushana, G. P.; Shivaramaiah, R.; Navrotsky, A. Direct Calorimetric Verification of Thermodynamic Instability of Lead Halide Hybrid Perovskites. *Proc. Natl. Acad. Sci. U. S. A.* **2016**, *113*, 7717–21.

(203) Ciccioli, A.; Latini, A. Thermodynamics and the Intrinsic Stability of Lead Halide Perovskites $\text{CH}_3\text{NH}_3\text{PbX}_3$. *J. Phys. Chem. Lett.* **2018**, *9*, 3756–3765.

(204) Cao, D. H.; Stoumpos, C. C.; Farha, O. K.; Hupp, J. T.; Kanatzidis, M. G. 2D Homologous Perovskites as Light-Absorbing Materials for Solar Cell Applications. *J. Am. Chem. Soc.* **2015**, *137*, 7843–50.

(205) Riedinger, A.; Ott, F. D.; Mule, A.; Mazzotti, S.; Knusel, P. N.; Kress, S. J. P.; Prins, F.; Erwin, S. C.; Norris, D. J. An Intrinsic Growth Instability in Isotropic Materials Leads to Quasi-Two-Dimensional Nanoplatelets. *Nat. Mater.* **2017**, *16*, 743–748.

(206) Burlakov, V. M.; Hassan, Y.; Danaie, M.; Snaith, H. J.; Goriely, A. Competitive Nucleation Mechanism for CsPbBr_3 Perovskite Nanoplatelet Growth. *J. Phys. Chem. Lett.* **2020**, *11*, 6535–6543.

(207) Paritmongkol, W.; Dahod, N. S.; Stollmann, A.; Mao, N.; Settens, C.; Zheng, S.-L.; Tisdale, W. A. Synthetic Variation and Structural Trends in Layered Two-Dimensional Alkylammonium Lead Halide Perovskites. *Chem. Mater.* **2019**, *31*, 5592–5607.

(208) Stoumpos, C. C.; Soe, C. M. M.; Tsai, H.; Nie, W.; Blancon, J.-C.; Cao, D. H.; Liu, F.; Traoré, B.; Katan, C.; Even, J.; Mohite, A. D.; Kanatzidis, M. G. High Members of the 2D Ruddlesden-Popper Halide Perovskites: Synthesis, Optical Properties, and Solar Cells of $(\text{CH}_3(\text{CH}_2)_3\text{NH}_3)_2(\text{CH}_3\text{NH}_3)_4\text{Pb}_5\text{I}_{16}$. *Chem.* **2017**, *2*, 427–440.

(209) Weidman, M. C.; Seitz, M.; Stranks, S. D.; Tisdale, W. A. Highly Tunable Colloidal Perovskite Nanoplatelets Through Variable Cation, Metal, and Halide Composition. *ACS Nano* **2016**, *10*, 7830–7839.

(210) Bertolotti, F.; Nedelcu, G.; Vivani, A.; Cervellino, A.; Masciocchi, N.; Guagliardi, A.; Kovalenko, M. V. Crystal Structure, Morphology, and Surface Termination of Cyan-Emissive, Six-Monolayers-Thick CsPbBr_3 Nanoplatelets from X-ray Total Scattering. *ACS Nano* **2019**, *13*, 14294–14307.

(211) Kumar, S.; Jagielski, J.; Yakunin, S.; Rice, P.; Chiu, Y.-C.; Wang, M.; Nedelcu, G.; Kim, Y.; Lin, S.; Santos, E. J.; Kovalenko, M. V.; Shih, C.-J. Efficient Blue Electroluminescence Using Quantum-Confined Two-Dimensional Perovskites. *ACS Nano* **2016**, *10*, 9720–9729.

(212) Zhao, J.; Cao, S.; Li, Z.; Ma, N. Amino Acid-Mediated Synthesis of CsPbBr_3 Perovskite Nanoplatelets with Tunable Thickness and Optical Properties. *Chem. Mater.* **2018**, *30*, 6737–6743.

(213) Shamsi, J.; Kubicki, D.; Anaya, M.; Liu, Y.; Ji, K.; Frohna, K.; Grey, C. P.; Friend, R. H.; Stranks, S. D. Stable Hexylphosphonate-Capped Blue-Emitting Quantum-Confined CsPbBr_3 Nanoplatelets. *ACS Energy Lett.* **2020**, *5*, 1900–1907.

(214) Ha, S. K.; Tisdale, W. A. Facile Synthesis of Colloidal Lead Halide Perovskite Nanoplatelets via Ligand-Assisted Reprecipitation. *J. Visualized Exp.* **2019**, *152*, No. e60114.

(215) Bonato, L. G.; Moral, R. F.; Nagamine, G.; Alo, A.; Germino, J. C.; da Silva, D. S.; Almeida, D. B.; Zagonel, L. F.; Galembeck, F.; Padilha, L. A.; Nogueira, A. F. Revealing the Role of Tin(IV) Halides in the Anisotropic Growth of CsPbX_3 Perovskite Nanoplates. *Angew. Chem., Int. Ed.* **2020**, *59*, 11501–11509.

(216) Yang, D.; Zou, Y.; Li, P.; Liu, Q.; Wu, L.; Hu, H.; Xu, Y.; Sun, B.; Zhang, Q.; Lee, S.-T. Large-Scale Synthesis of Ultrathin Cesium Lead Bromide Perovskite Nanoplates with Precisely Tunable Dimensions and Their Application in Blue Light-Emitting Diodes. *Nano Energy* **2018**, *47*, 235–242.

(217) Shamsi, J.; Dang, Z.; Bianchini, P.; Canale, C.; Di Stasio, F.; Brescia, R.; Prato, M.; Manna, L. Colloidal Synthesis of Quantum Confined Single Crystal CsPbBr_3 Nanosheets with Lateral Size Control up to the Micrometer Range. *J. Am. Chem. Soc.* **2016**, *138*, 7240–7243.

(218) Zhang, Y.; Wang, C.; Deng, Z. Colloidal Synthesis of Monolayer-Thick Formamidinium Lead Bromide Perovskite Nanosheets with a Lateral Size of Micrometers. *Chem. Commun.* **2018**, *54*, 4021–4024.

(219) Yang, S.; Niu, W.; Wang, A.-L.; Fan, Z.; Chen, B.; Tan, C.; Lu, Q.; Zhang, H. Ultrathin Two-Dimensional Organic–Inorganic Hybrid Perovskite Nanosheets with Bright, Tunable Photoluminescence and High Stability. *Angew. Chem., Int. Ed.* **2017**, *56*, 4252–4255.

(220) Yuan, Z.; Shu, Y.; Xin, Y.; Ma, B. Highly Luminescent Nanoscale Quasi-2D Layered Lead Bromide Perovskites with Tunable Emissions. *Chem. Commun.* **2016**, *52*, 3887–90.

(221) Wei, M.; de Arquer, F. P. G.; Walters, G.; Yang, Z.; Quan, L. N.; Kim, Y.; Sabatini, R.; Quintero-Bermudez, R.; Gao, L.; Fan, J. Z.; Fan, F.; Gold-Parker, A.; Toney, M. F.; Sargent, E. H. Ultrafast Narrowband Exciton Routing within Layered Perovskite Nanoplatelets Enables Low-Loss Luminescent Solar Concentrators. *Nat. Energy* **2019**, *4*, 197–205.

(222) Jagielski, J.; Kumar, S.; Yu, W.-Y.; Shih, C.-J. Layer-Controlled Two-Dimensional Perovskites: Synthesis and Optoelectronics. *J. Mater. Chem. C* **2017**, *5*, 5610–5627.

(223) Huang, S.; Li, Z.; Wang, B.; Zhu, N.; Zhang, C.; Kong, L.; Zhang, Q.; Shan, A.; Li, L. Morphology Evolution and Degradation of CsPbBr_3 Nanocrystals under Blue Light-Emitting Diode Illumination. *ACS Appl. Mater. Interfaces* **2017**, *9*, 7249–7258.

(224) Han, D.; Imran, M.; Zhang, M.; Chang, S.; Wu, X.-g.; Zhang, X.; Tang, J.; Wang, M.; Ali, S.; Li, X.; Yu, G.; Han, J.; Wang, L.; Zou, B.; Zhong, H. Efficient Light-Emitting Diodes Based on *in Situ* Fabricated FAPbBr_3 Nanocrystals: The Enhancing Role of the Ligand-Assisted Reprecipitation Process. *ACS Nano* **2018**, *12*, 8808–8816.

(225) Mehetor, S. K.; Ghosh, H.; Pradhan, N. Acid-Amine Equilibria for Formation and Long-Range Self-Organization of Ultrathin CsPbBr_3 Perovskite Platelets. *J. Phys. Chem. Lett.* **2019**, *10*, 1300–1305.

(226) Wu, Y.; Wei, C.; Li, X.; Li, Y.; Qiu, S.; Shen, W.; Cai, B.; Sun, Z.; Yang, D.; Deng, Z.; Zeng, H. *In Situ* Passivation of PbBr_6^{4-} Octahedra toward Blue Luminescent CsPbBr_3 Nanoplatelets with Near 100% Absolute Quantum Yield. *ACS Energy Lett.* **2018**, *3*, 2030–2037.

(227) DeCrescent, R. A.; Venkatesan, N. R.; Dahlman, C. J.; Kennard, R. M.; Chabinyc, M. L.; Schuller, J. A. Optical Constants and Effective-Medium Origins of Large Optical Anisotropies in Layered Hybrid Organic/Inorganic Perovskites. *ACS Nano* **2019**, *13*, 10745–10753.

(228) Jurow, M. J.; Morgenstern, T.; Eisler, C.; Kang, J.; Penzo, E.; Do, M. Q.; Engelmayr, M.; Osowiecki, W. T.; Bekenstein, Y.; Tassone, C. J.; Wang, L.-W.; Alivisatos, A. P.; Brutting, W.; Liu, Y. Manipulating the Transition Dipole Moment of CsPbBr_3 Perovskite

Nanocrystals for Superior Optical Properties. *Nano Lett.* **2019**, *19*, 2489–2496.

(229) Ha, S. K.; Mauck, C. M.; Tisdale, W. A. Toward Stable Deep-Blue Luminescent Colloidal Lead Halide Perovskite Nanoplatelets: Systematic Photostability Investigation. *Chem. Mater.* **2019**, *31*, 2486–2496.

(230) Nistal, A.; Garcia, E.; Pérez -Coll, D.; Prieto, C.; Belmonte, M.; Osendi, M. I.; Miranzo, P. Low Percolation Threshold in Highly Conducting Graphene Nanoplatelets/Glass Composite Coatings. *Carbon* **2018**, *139*, 556–563.

(231) Tong, Y.; Ehrat, F.; Vanderlinden, W.; Cardenas-Daw, C.; Stolarczyk, J. K.; Polavarapu, L.; Urban, A. S. Dilution-Induced Formation of Hybrid Perovskite Nanoplatelets. *ACS Nano* **2016**, *10*, 10936–10944.

(232) Cho, J.; Choi, Y.-H.; O'Loughlin, T. E.; De Jesus, L.; Banerjee, S. Ligand-Mediated Modulation of Layer Thicknesses of Perovskite Methylammonium Lead Bromide Nanoplatelets. *Chem. Mater.* **2016**, *28*, 6909–6916.

(233) Seth, S.; Samanta, A. A Facile Methodology for Engineering the Morphology of CsPbX_3 Perovskite Nanocrystals under Ambient Condition. *Sci. Rep.* **2016**, *6*, 37693.

(234) Shamsi, J.; Rastogi, P.; Caligiuri, V.; Abdelhady, A. L.; Spirito, D.; Manna, L.; Krahne, R. Bright-Emitting Perovskite Films by Large-Scale Synthesis and Photoinduced Solid-State Transformation of CsPbBr_3 Nanoplatelets. *ACS Nano* **2017**, *11*, 10206–10213.

(235) Wang, Y.; Li, X.; Sreejith, S.; Cao, F.; Wang, Z.; Stuparu, M. C.; Zeng, H.; Sun, H. Photon Driven Transformation of Cesium Lead Halide Perovskites from Few-Monolayer Nanoplatelets to Bulk Phase. *Adv. Mater.* **2016**, *28*, 10637–10643.

(236) Liang, Z.; Zhao, S.; Xu, Z.; Qiao, B.; Song, P.; Gao, D.; Xu, X. Shape-Controlled Synthesis of All-Inorganic CsPbBr_3 Perovskite Nanocrystals with Bright Blue Emission. *ACS Appl. Mater. Interfaces* **2016**, *8*, 28824–28830.

(237) Dahlman, C. J.; Venkatesan, N. R.; Corona, P. T.; Kennard, R. M.; Mao, L.; Smith, N. C.; Zhang, J.; Seshadri, R.; Helgeson, M. E.; Chabinyc, M. L. Structural Evolution of Layered Hybrid Lead Iodide Perovskites in Colloidal Dispersions. *ACS Nano* **2020**, *14*, 11294–11308.

(238) Mir, W. J.; Jagadeeswararao, M.; Das, S.; Nag, A. Colloidal Mn-Doped Cesium Lead Halide Perovskite Nanoplatelets. *ACS Energy Lett.* **2017**, *2*, 537–543.

(239) Gao, M. Y.; Liu, H.; Yu, S.; Louisiana, S.; Zhang, Y.; Nenon, D. P.; Alivisatos, A. P.; Yang, P. D. Scaling Laws of Exciton Recombination Kinetics in Low Dimensional Halide Perovskite Nanostructures. *J. Am. Chem. Soc.* **2020**, *142*, 8871–8879.

(240) Lai, M.; Kong, Q.; Bischak, C. G.; Yu, Y.; Dou, L.; Eaton, S. W.; Ginsberg, N. S.; Yang, P. Structural, Optical, and Electrical Properties of Phase-Controlled Cesium Lead Iodide Nanowires. *Nano Res.* **2017**, *10*, 1107–1114.

(241) Wong, A. B.; Lai, M. L.; Eaton, S. W.; Yu, Y.; Lin, E.; Dou, L.; Fu, A.; Yang, P. D. Growth and Anion Exchange Conversion of $\text{CH}_3\text{NH}_3\text{PbX}_3$ Nanorod Arrays for Light-Emitting Diodes. *Nano Lett.* **2015**, *15*, 5519–5524.

(242) Fu, Y. P.; Zhu, H. M.; Schrader, A. W.; Liang, D.; Ding, Q.; Joshi, P.; Hwang, L.; Zhu, X. Y.; Jin, S. Nanowire Lasers of Formamidinium Lead Halide Perovskites and Their Stabilized Alloys with Improved Stability. *Nano Lett.* **2016**, *16*, 1000–1008.

(243) Lei, T.; Lai, M. L.; Kong, Q.; Lu, D. Y.; Lee, W.; Dou, L. T.; Wu, V.; Yu, Y.; Yang, P. D. Electrical and Optical Tunability in All-Inorganic Halide Perovskite Alloy Nanowires. *Nano Lett.* **2018**, *18*, 3538–3542.

(244) Eaton, S. W.; Lai, M. L.; Gibson, N. A.; Wong, A. B.; Dou, L. T.; Ma, J.; Wang, L. W.; Leone, S. R.; Yang, P. D. Lasing in Robust Cesium Lead Halide Perovskite Nanowires. *Proc. Natl. Acad. Sci. U. S. A.* **2016**, *113*, 1993–1998.

(245) Dai, J.; Fu, Y. P.; Manger, L. H.; Rea, M. T.; Hwang, L.; Goldsmith, R. H.; Jin, S. Carrier Decay Properties of Mixed Cation Formamidinium-Methylammonium Lead Iodide Perovskite $[\text{HC}$

$(\text{NH}_2)_2]_{(1-x)}[\text{CH}_3\text{NH}_3]_x\text{PbI}_3$ Nanorods. *J. Phys. Chem. Lett.* **2016**, *7*, 5036–5043.

(246) Chen, J.; Fu, Y. P.; Samad, L.; Dang, L. N.; Zhao, Y. Z.; Shen, S. H.; Guo, L. J.; Jin, S. Vapor-Phase Epitaxial Growth of Aligned Nanowire Networks of Cesium Lead Halide Perovskites (CsPbX_3 , X = Cl, Br, I). *Nano Lett.* **2017**, *17*, 460–466.

(247) Zhou, H.; Yuan, S.; Wang, X.; Xu, T.; Wang, X.; Li, H.; Zheng, W.; Fan, P.; Li, Y.; Sun, L.; Pan, A. Vapor Growth and Tunable Lasing of Band Gap Engineered Cesium Lead Halide Perovskite Micro/Nanorods with Triangular Cross Section. *ACS Nano* **2017**, *11*, 1189–1195.

(248) Wang, Y. P.; Sun, X.; Shivanna, R.; Yang, Y. B.; Chen, Z. Z.; Guo, Y. W.; Wang, G. C.; Wertz, E.; Deschler, F.; Cai, Z. H.; Zhou, H.; Lu, T. M.; Shi, J. Photon Transport in One-Dimensional Incommensurately Epitaxial CsPbX_3 Arrays. *Nano Lett.* **2016**, *16*, 7974–7981.

(249) Lu, D.; Zhang, Y.; Lai, M. L.; Lee, A.; Xie, C. L.; Lin, J.; Lei, T.; Lin, Z. N.; Kley, C. S.; Huang, J. M.; Rabani, E.; Yang, P. D. Giant Light-Emission Enhancement in Lead Halide Perovskites by Surface Oxygen Passivation. *Nano Lett.* **2018**, *18*, 6967–6973.

(250) Shoaib, M.; Zhang, X.; Wang, X.; Zhou, H.; Xu, T.; Wang, X.; Hu, X.; Liu, H.; Fan, X.; Zheng, W.; Yang, T.; Yang, S.; Zhang, Q.; Zhu, X.; Sun, L.; Pan, A. Directional Growth of Ultralong CsPbBr_3 Perovskite Nanowires for High-Performance Photodetectors. *J. Am. Chem. Soc.* **2017**, *139*, 15592–15595.

(251) Oksenberg, E.; Sanders, E.; Popovitz-Biro, R.; Houben, L.; Joselevich, E. Surface-Guided CsPbBr_3 Perovskite Nanowires on Flat and Faceted Sapphire with Size-Dependent Photoluminescence and Fast Photoconductive Response. *Nano Lett.* **2018**, *18*, 424–433.

(252) Dou, L.; Lai, M. L.; Kley, C. S.; Yang, Y. M.; Bischak, C. G.; Zhang, D. D.; Eaton, S. W.; Ginsberg, N. S.; Yang, P. D. Spatially Resolved Multicolor CsPbX_3 Nanowire Heterojunctions via Anion Exchange. *Proc. Natl. Acad. Sci. U. S. A.* **2017**, *114*, 7216–7221.

(253) Kong, Q.; Obliger, A.; Lai, M.; Gao, M.; Limmer, D. T.; Yang, P. Solid-State Ionic Rectification in Perovskite Nanowire Heterostructures. *Nano Lett.* **2020**, *20*, 8151–8156.

(254) Nah, S.; Spokoyny, B.; Stoumpos, C.; Soe, C. M. M.; Kanatzidis, M.; Harel, E. Spatially Segregated Free-Carrier and Exciton Populations in Individual Lead Halide Perovskite Grains. *Nat. Photonics* **2017**, *11*, 285–288.

(255) Lai, M. L.; Obliger, A.; Lu, D.; Kley, C. S.; Bischak, C. G.; Kong, Q.; Lei, T.; Dou, L. T.; Ginsberg, N. S.; Limmer, D. T.; Yang, P. D. Intrinsic Anion Diffusivity in Lead Halide Perovskites is Facilitated by A Soft Lattice. *Proc. Natl. Acad. Sci. U. S. A.* **2018**, *115*, 11929–11934.

(256) Pan, D.; Fu, Y.; Chen, J.; Czech, K. J.; Wright, J. C.; Jin, S. Visualization and Studies of Ion-Diffusion Kinetics in Cesium Lead Bromide Perovskite Nanowires. *Nano Lett.* **2018**, *18* (3), 1807–1813.

(257) Bischak, C. G.; Lai, M.; Fan, Z.; Lu, D.; David, P.; Dong, D.; Chen, H.; Etman, A. S.; Lei, T.; Sun, J.; Grunwald, M.; Limmer, D. T.; Yang, P.; Ginsberg, N. S. Liquid-like Interfaces Mediate Structural Phase Transitions in Lead Halide Perovskites. *Matter* **2020**, *3*, P534–P545.

(258) Kong, Q.; Lee, W.; Lai, M. L.; Bischak, C. G.; Gao, G. P.; Wong, A. B.; Lei, T.; Yu, Y.; Wang, L. W.; Ginsberg, N. S.; Yang, P. D. Phase-Transition-Induced *p-n* Junction in Single Halide Perovskite Nanowire. *Proc. Natl. Acad. Sci. U. S. A.* **2018**, *115*, 8889–8894.

(259) Lee, W.; Li, H. S.; Wong, A. B.; Zhang, D. D.; Lai, M. L.; Yu, Y.; Kong, Q.; Lin, E.; Urban, J. J.; Grossman, J. C.; Yang, P. D. Ultralow Thermal Conductivity in All-Inorganic Halide Perovskites. *Proc. Natl. Acad. Sci. U. S. A.* **2017**, *114*, 8693–8697.

(260) Wang, Y.; Lin, R.; Zhu, P.; Zheng, Q.; Wang, Q.; Li, D.; Zhu, J. Cation Dynamics Governed Thermal Properties of Lead Halide Perovskite Nanowires. *Nano Lett.* **2018**, *18*, 2772–2779.

(261) Zhu, P.; Gu, S.; Shen, X.; Xu, N.; Tan, Y.; Zhuang, S.; Deng, Y.; Lu, Z.; Wang, Z.; Zhu, J. Direct Conversion of Perovskite Thin Films into Nanowires with Kinetic Control for Flexible Optoelectronic Devices. *Nano Lett.* **2016**, *16*, 871–876.

(262) Zhang, X.; Chen, S.; Wang, X.; Pan, A. Controlled Synthesis and Photonics Applications of Metal Halide Perovskite Nanowires. *Small Methods* **2019**, *3*, 1800294.

(263) Gao, L.; Zeng, K.; Guo, J.; Ge, C.; Du, J.; Zhao, Y.; Chen, C.; Deng, H.; He, Y.; Song, H.; Niu, G.; Tang, J. Passivated Single-Crystalline $\text{CH}_3\text{NH}_3\text{PbI}_3$ Nanowire Photodetector with High Detectivity and Polarization Sensitivity. *Nano Lett.* **2016**, *16*, 7446–7454.

(264) Singh, R.; Suranagi, S. R.; Yang, S. J.; Cho, K. Enhancing the Power Conversion Efficiency of Perovskite Solar Cells *via* the Controlled Growth of Perovskite Nanowires. *Nano Energy* **2018**, *51*, 192–198.

(265) Wang, S.; Yan, S.; Wang, M.; Chang, L.; Wang, J.; Wang, Z. Construction of Nanowire $\text{CH}_3\text{NH}_3\text{PbI}_3$ -Based Solar Cells with 17.62% Efficiency by Solvent Etching Technique. *Sol. Energy Mater. Sol. Cells* **2017**, *167*, 173–177.

(266) Horváth, E.; Spina, M.; Szekrényes, Z.; Kamarás, K.; Gaal, R.; Gachet, D.; Forró, L. Nanowires of Methylammonium Lead Iodide ($\text{CH}_3\text{NH}_3\text{PbI}_3$) Prepared by Low Temperature Solution-Mediated Crystallization. *Nano Lett.* **2014**, *14*, 6761–6766.

(267) Im, J.-H.; Luo, J.; Frankevičius, M.; Pellet, N.; Gao, P.; Moehl, T.; Zakeeruddin, S. M.; Nazeeruddin, M. K.; Grätzel, M.; Park, N.-G. Nanowire Perovskite Solar Cell. *Nano Lett.* **2015**, *15*, 2120–2126.

(268) Petrov, A. A.; Pellet, N.; Seo, J.-Y.; Belich, N. A.; Kovalev, D. Y.; Shevelkov, A. V.; Goodilin, E. A.; Zakeeruddin, S. M.; Tarasov, A. B.; Graetzel, M. New Insight into the Formation of Hybrid Perovskite Nanowires *via* Structure Directing Adducts. *Chem. Mater.* **2017**, *29*, 587–594.

(269) Spina, M.; Bonvin, E.; Sienkiewicz, A.; Náfrádi, B.; Forró, L.; Horváth, E. Controlled Growth of $\text{CH}_3\text{NH}_3\text{PbI}_3$ Nanowires in Arrays of Open Nanofluidic Channels. *Sci. Rep.* **2016**, *6*, 19834.

(270) Ashley, M. J.; O'Brien, M. N.; Hedderick, K. R.; Mason, J. A.; Ross, M. B.; Mirkin, C. A. Templated Synthesis of Uniform Perovskite Nanowire Arrays. *J. Am. Chem. Soc.* **2016**, *138*, 10096–10099.

(271) Xing, J.; Liu, X. F.; Zhang, Q.; Ha, S. T.; Yuan, Y. W.; Shen, C.; Sum, T. C.; Xiong, Q. Vapor Phase Synthesis of Organometal Halide Perovskite Nanowires for Tunable Room-Temperature Nanolasers. *Nano Lett.* **2015**, *15*, 4571–4577.

(272) Zhang, F.; Chen, C.; Kershaw, S. V.; Xiao, C.; Han, J.; Zou, B.; Wu, X.; Chang, S.; Dong, Y.; Rogach, A. L.; Zhong, H. Ligand-Controlled Formation and Photoluminescence Properties of $\text{CH}_3\text{NH}_3\text{PbBr}_3$ Nanocubes and Nanowires. *ChemNanoMat* **2017**, *3*, 303–310.

(273) Debroye, E.; Yuan, H.; Bladt, E.; Baekelant, W.; Van der Auweraer, M.; Hofkens, J.; Bals, S.; Roeffaers, M. B. J. Facile Morphology-Controlled Synthesis of Organolead Iodide Perovskite Nanocrystals Using Binary Capping Agents. *ChemNanoMat* **2017**, *3*, 223–227.

(274) Xuan, T.; Yang, X.; Lou, S.; Huang, J.; Liu, Y.; Yu, J.; Li, H.; Wong, K.-L.; Wang, C.; Wang, J. Highly Stable CsPbBr_3 Quantum Dots Coated With Alkyl Phosphate for White Light-Emitting Diodes. *Nanoscale* **2017**, *9* (40), 15286–15290.

(275) Liu, L. C.; Risbud, S. H. Quantum-Dot Size-Distribution Analysis and Precipitation Stages in Semiconductor Doped Glasses. *J. Appl. Phys.* **1990**, *68*, 28–32.

(276) Xu, K.; Liu, C.; Chung, W. J.; Heo, J. Optical Properties of CdSe Quantum Dots in Silicate Glasses. *J. Non-Cryst. Solids* **2010**, *356*, 2299–2301.

(277) Nagabhushana, G. P.; Shivaramaiah, R.; Navrotsky, A. Direct Calorimetric Verification of Thermodynamic Instability of Lead Halide Hybrid Perovskites. *Proc. Natl. Acad. Sci. U. S. A.* **2016**, *113*, 7717–7721.

(278) Zhou, Q.; Bai, Z.; Lu, W.-g.; Wang, Y.; Zou, B.; Zhong, H. *In Situ* Fabrication of Halide Perovskite Nanocrystal-Embedded Polymer Composite Films with Enhanced Photoluminescence for Display Backlights. *Adv. Mater.* **2016**, *28*, 9163–9168.

(279) Kojima, A.; Ikegami, M.; Teshima, K.; Miyasaka, T. Highly Luminescent Lead Bromide Perovskite Nanoparticles Synthesized with Porous Alumina Media. *Chem. Lett.* **2012**, *41*, 397–399.

(280) Liu, S.; He, M.; Di, X.; Li, P.; Xiang, W.; Liang, X. Precipitation and Tunable Emission of Cesium Lead Halide Perovskites (CsPbX_3 , X = Br, I) QDs in Borosilicate Glass. *Ceram. Int.* **2018**, *44*, 4496–4499.

(281) Shen, L.; Zhang, Z.; Zhao, Y.; Yang, H.; Yuan, L.; Chen, Y.; Xiang, W.; Liang, X. Synthesis and Optical Properties of Novel Mixed-Metal Cation $\text{CsPb}_{1-x}\text{Ti}_x\text{Br}_3$ -based Perovskite Glasses for W-LED. *J. Am. Ceram. Soc.* **2020**, *103*, 382–390.

(282) Huang, X.; Guo, Q.; Yang, D.; Xiao, X.; Liu, X.; Xia, Z.; Fan, F.; Qiu, J.; Dong, G. Reversible 3D Laser Printing of Perovskite Quantum Dots inside a Transparent Medium. *Nat. Photonics* **2020**, *14*, 82–88.

(283) Zhang, Q.; Wang, B.; Zheng, W.; Kong, L.; Wan, Q.; Zhang, C.; Li, Z.; Cao, X.; Liu, M.; Li, L. Ceramic-Like Stable CsPbBr_3 Nanocrystals Encapsulated in Silica Derived from Molecular Sieve Templates. *Nat. Commun.* **2020**, *11*, 31.

(284) Chen, N.; Bai, Z.; Wang, Z.; Ji, H.; Liu, R.; Cao, C.; Wang, H.; Jiang, F.; Zhong, H. P-119: Low Cost Perovskite Quantum Dots Film Based Wide Color Gamut Backlight Unit for LCD TVs. *Dig. Tech. Pap. - Soc. Inf. Disp. Int. Symp.* **2018**, *49*, 1657–1659.

(285) Wang, Y.; He, J.; Chen, H.; Chen, J.; Zhu, R.; Ma, P.; Towers, A.; Lin, Y.; Gesquiere, A. J.; Wu, S.-T.; Dong, Y. Ultrastable, Highly Luminescent Organic-Inorganic Perovskite-Polymer Composite Films. *Adv. Mater.* **2016**, *28*, 10710–10717.

(286) Kang, S.-M.; Park, B.; Raju, G. S. R.; Baek, S.; Hussain, S. K.; Kwak, C. H.; Han, Y.-K.; Yu, J. S.; Kim, S.-W.; Huh, Y. S. Generation of Cesium Lead Halide Perovskite Nanocrystals *via* a Serially-Integrated Microreactor System: Sequential Anion Exchange Reaction. *Chem. Eng. J.* **2020**, *384*, 123316.

(287) Koscher, B. A.; Bronstein, N. D.; Olshansky, J. H.; Bekenstein, Y.; Alivisatos, A. P. Surface- vs Diffusion-Limited Mechanisms of Anion Exchange in CsPbBr_3 Nanocrystal Cubes Revealed through Kinetic Studies. *J. Am. Chem. Soc.* **2016**, *138*, 12065–12068.

(288) Zhang, Y.; Lu, D.; Gao, M.; Lai, M.; Lin, J.; Lei, T.; Lin, Z.; Quan, L. N.; Yang, P. Quantitative Imaging of Anion Exchange Kinetics in Halide Perovskites. *Proc. Natl. Acad. Sci. U. S. A.* **2019**, *116*, 12648.

(289) Wang, D.; Cavin, J.; Yin, B.; Thind, A. S.; Borisevich, A. Y.; Mishra, R.; Sadtler, B. Role of Solid-State Miscibility during Anion Exchange in Cesium Lead Halide Nanocrystals Probed by Single-Particle Fluorescence. *J. Phys. Chem. Lett.* **2020**, *11*, 952–959.

(290) Haque, A.; Ravi, V. K.; Shanker, G. S.; Sarkar, I.; Nag, A.; Santra, P. K. Internal Heterostructure of Anion-Exchanged Cesium Lead Halide Nanocubes. *J. Phys. Chem. C* **2018**, *122*, 13399–13406.

(291) Loijudice, A.; Strach, M.; Saris, S.; Chernyshov, D.; Buonsanti, R. Universal Oxide Shell Growth Enables *In Situ* Structural Studies of Perovskite Nanocrystals during the Anion Exchange Reaction. *J. Am. Chem. Soc.* **2019**, *141*, 8254–8263.

(292) Hoffman, J. B.; Schleper, A. L.; Kamat, P. V. Transformation of Sintered CsPbBr_3 Nanocrystals to Cubic CsPbI_3 and Gradient $\text{CsPbBr}_x\text{I}_{3-x}$ through Halide Exchange. *J. Am. Chem. Soc.* **2016**, *138*, 8603–8611.

(293) Elmelund, T.; Scheidt, R. A.; Seger, B.; Kamat, P. V. Bidirectional Halide Ion Exchange in Paired Lead Halide Perovskite Films with Thermal Activation. *ACS Energy Lett.* **2019**, *4*, 1961–1969.

(294) Scheidt, R. A.; Kamat, P. V. Temperature-Driven Anion Migration in Gradient Halide Perovskites. *J. Chem. Phys.* **2019**, *151*, 134703.

(295) Ravi, V. K.; Scheidt, R. A.; DuBose, J.; Kamat, P. V. Hierarchical Arrays of Cesium Lead Halide Perovskite Nanocrystals through Electrophoretic Deposition. *J. Am. Chem. Soc.* **2018**, *140*, 8887–8894.

(296) Ravi, V. K.; Scheidt, R. A.; Nag, A.; Kuno, M.; Kamat, P. V. To Exchange or Not to Exchange. Suppressing Anion Exchange in Cesium Lead Halide Perovskites with PbSO_4^- Oleate Capping. *ACS Energy Lett.* **2018**, *3*, 1049–1055.

(297) Palazon, F.; Akkerman, Q. A.; Prato, M.; Manna, L. X-ray Lithography on Perovskite Nanocrystals Films: From Patterning with Anion-Exchange Reactions to Enhanced Stability in Air and Water. *ACS Nano* **2016**, *10*, 1224–1230.

(298) Xiao, X.; Dai, J.; Fang, Y.; Zhao, J.; Zheng, X.; Tang, S.; Rudd, P. N.; Zeng, X. C.; Huang, J. Suppressed Ion Migration along the In-Plane Direction in Layered Perovskites. *ACS Energy Lett.* **2018**, *3*, 684–688.

(299) Rivest, J. B.; Jain, P. K. Cation Exchange on the Nanoscale: An Emerging Technique for New Material Synthesis, Device Fabrication, and Chemical Sensing. *Chem. Soc. Rev.* **2013**, *42*, 89–96.

(300) Xie, Y.-M.; Yu, B.; Ma, C.; Xu, X.; Cheng, Y.; Yuan, S.; Wang, Z.-K.; Chandran, H. T.; Lee, C.-S.; Liao, L.-S.; Tsang, S.-W. Direct Observation of Cation-Exchange in Liquid-to-Solid Phase Transformation in $\text{FA}_{1-x}\text{MA}_x\text{PbI}_3$ Based Perovskite Solar Cells. *J. Mater. Chem. A* **2018**, *6*, 9081–9088.

(301) Wang, B.; Zhang, C.; Huang, S.; Li, Z.; Kong, L.; Jin, L.; Wang, J.; Wu, K.; Li, L. Postsynthesis Phase Transformation for $\text{CsPbBr}_3/\text{Rb}_4\text{PbBr}_6$ Core/Shell Nanocrystals with Exceptional Photo-stability. *ACS Appl. Mater. Interfaces* **2018**, *10*, 23303–23310.

(302) Huang, W.; Wang, Y.; Balakrishnan, S. K. Controllable Transformation between 3D and 2D perovskites through Cation Exchange. *Chem. Commun.* **2018**, *54*, 7944–7947.

(303) Lau, C. F. J.; Wang, Z.; Sakai, N.; Zheng, J.; Liao, C. H.; Green, M.; Huang, S.; Snaith, H. J.; Ho-Baillie, A. Fabrication of Efficient and Stable CsPbI_3 Perovskite Solar Cells through Cation Exchange Process. *Adv. Energy Mater.* **2019**, *9*, 1901685.

(304) van der Stam, W.; Geuchies, J. J.; Altantzis, T.; van den Bos, K. H. W.; Meeldijk, J. D.; Van Aert, S.; Bals, S.; Vanmaekelbergh, D.; de Mello Donega, C. Highly Emissive Divalent-Ion-Doped Colloidal $\text{CsPb}_{1-x}\text{M}_x\text{Br}_3$ Perovskite Nanocrystals through Cation Exchange. *J. Am. Chem. Soc.* **2017**, *139*, 4087–4097.

(305) Roman, B. J.; Otto, J.; Galik, C.; Downing, R.; Sheldon, M. Au Exchange or Au Deposition: Dual Reaction Pathways in Au– CsPbBr_3 Heterostructure Nanoparticles. *Nano Lett.* **2017**, *17*, 5561–5566.

(306) Li, M.; Zhang, X.; Matras-Postolek, K.; Chen, H.-S.; Yang, P. P. An Anion-Driven Sn^{2+} Exchange Reaction in CsPbBr_3 Nanocrystals towards Tunable and High Photoluminescence. *J. Mater. Chem. C* **2018**, *6*, 5506–5513.

(307) Eames, C.; Frost, J. M.; Barnes, P. R. F.; O'Regan, B. C.; Walsh, A.; Islam, M. S. Ionic Transport in Hybrid Lead Iodide Perovskite Solar Cells. *Nat. Commun.* **2015**, *6*, 7497.

(308) Gao, D.; Qiao, B.; Xu, Z.; Song, D.; Song, P.; Liang, Z.; Shen, Z.; Cao, J.; Zhang, J.; Zhao, S. Postsynthetic, Reversible Cation Exchange between Pb^{2+} and Mn^{2+} in Cesium Lead Chloride Perovskite Nanocrystals. *J. Phys. Chem. C* **2017**, *121*, 20387–20395.

(309) Fang, G.; Chen, D.; Zhou, S.; Chen, X.; Lei, L.; Zhong, J.; Ji, Z. Reverse Synthesis of $\text{CsPb}_x\text{Mn}_{1-x}(\text{Cl}/\text{Br})_3$ Perovskite Quantum Dots from CsMnCl_3 Precursors through Cation Exchange. *J. Mater. Chem. C* **2018**, *6*, 5908–5915.

(310) Eperon, G. E.; Ginger, D. S. B-Site Metal Cation Exchange in Halide Perovskites. *ACS Energy Lett.* **2017**, *2*, 1190–1196.

(311) Li, F.; Xia, Z.; Pan, C.; Gong, Y.; Gu, L.; Liu, Q.; Zhang, J. Z. High Br– Content $\text{CsPb}(\text{Cl}_y\text{Br}_{1-y})_3$ Perovskite Nanocrystals with Strong Mn^{2+} Emission through Diverse Cation/Anion Exchange Engineering. *ACS Appl. Mater. Interfaces* **2018**, *10*, 11739–11746.

(312) Qiao, T.; Parobek, D.; Dong, Y.; Ha, E.; Son, D. H. Photoinduced Mn Doping in Cesium Lead Halide Perovskite Nanocrystals. *Nanoscale* **2019**, *11*, 5247–5253.

(313) Zhou, S.; Zhu, Y.; Zhong, J.; Tian, F.; Huang, H.; Chen, J.; Chen, D. Chlorine-Additive-Promoted Incorporation of Mn^{2+} Dopants into CsPbCl_3 Perovskite Nanocrystals. *Nanoscale* **2019**, *11*, 12465–12470.

(314) Shapiro, A.; Heindl, M. W.; Horani, F.; Dahan, M.-H.; Tang, J.; Amouyal, Y.; Lifshitz, E. Significance of Ni Doping in CsPbX_3 Nanocrystals via Postsynthesis Cation–Anion Coexchange. *J. Phys. Chem. C* **2019**, *123*, 24979–24987.

(315) Yuan, X.; Hou, X.; Li, J.; Qu, C.; Zhang, W.; Zhao, J.; Li, H. Thermal Degradation of Luminescence in Inorganic Perovskite CsPbBr_3 Nanocrystals. *Phys. Chem. Chem. Phys.* **2017**, *19*, 8934–8940.

(316) Peng, L.; Dutta, A.; Xie, R.; Yang, W.; Pradhan, N. Dot–Wire–Platelet–Cube: Step Growth and Structural Transformations in CsPbBr_3 Perovskite Nanocrystals. *ACS Energy Lett.* **2018**, *3*, 2014–2020.

(317) Pradhan, B.; Mushtaq, A.; Roy, D.; Sain, S.; Das, B.; Ghorai, U. K.; Pal, S. K.; Acharya, S. Postsynthesis Spontaneous Coalescence of Mixed-Halide Perovskite Nanocubes into Phase-Stable Single-Crystalline Uniform Luminescent Nanowires. *J. Phys. Chem. Lett.* **2019**, *10*, 1805–1812.

(318) Pan, J.; Li, X.; Gong, X.; Yin, J.; Zhou, D.; Sinatra, L.; Huang, R.; Liu, J.; Chen, J.; Dursun, I.; El-Zohry, A. M.; Saidaminov, M. I.; Sun, H.-T.; Mohammed, O. F.; Ye, C.; Sargent, E. H.; Bakr, O. M. Halogen Vacancies Enable Ligand-Assisted Self-Assembly of Perovskite Quantum Dots into Nanowires. *Angew. Chem., Int. Ed.* **2019**, *58*, 16077–16081.

(319) Dang, Z.; Dhanabalan, B.; Castelli, A.; Dhall, R.; Bustillo, K. C.; Marchelli, D.; Spirito, D.; Petralanda, U.; Shamsi, J.; Manna, L.; Krahne, R.; Arciniegas, M. P. Temperature-Driven Transformation of CsPbBr_3 Nanoplatelets into Mosaic Nanotiles in Solution through Self-Assembly. *Nano Lett.* **2020**, *20*, 1808–1818.

(320) Hudait, B.; Dutta, S. K.; Patra, A.; Nasipuri, D.; Pradhan, N. Facets Directed Connecting Perovskite Nanocrystals. *J. Am. Chem. Soc.* **2020**, *142*, 7207–7217.

(321) Liu, P.; Chen, W.; Wang, W.; Xu, B.; Wu, D.; Hao, J.; Cao, W.; Fang, F.; Li, Y.; Zeng, Y.; Pan, R.; Chen, S.; Cao, W.; Sun, X. W.; Wang, K. Halide-Rich Synthesized Cesium Lead Bromide Perovskite Nanocrystals for Light-Emitting Diodes with Improved Performance. *Chem. Mater.* **2017**, *29*, 5168–5173.

(322) Nagaoka, Y.; Hills-Kimball, K.; Tan, R.; Li, R.; Wang, Z.; Chen, O. Nanocube Superlattices of Cesium Lead Bromide Perovskites and Pressure-Induced Phase Transformations at Atomic and Mesoscale Levels. *Adv. Mater.* **2017**, *29*, 1606666.

(323) Fanizza, E.; Cascella, F.; Altamura, D.; Giannini, C.; Panniello, A.; Triggiani, L.; Panzarea, F.; Depalo, N.; Grisorio, R.; Suranna, G. P.; Agostiano, A.; Curri, M. L.; Striccoli, M. Post-Synthesis Phase and Shape Evolution of CsPbBr_3 Colloidal Nanocrystals: The Role of Ligands. *Nano Res.* **2019**, *12*, 1155–1166.

(324) Liu, L.; Huang, S.; Pan, L.; Shi, L.-J.; Zou, B.; Deng, L.; Zhong, H. Colloidal Synthesis of $\text{CH}_3\text{NH}_3\text{PbBr}_3$ Nanoplatelets with Polarized Emission through Self-Organization. *Angew. Chem., Int. Ed.* **2017**, *56*, 1780–1783.

(325) Xu, S.; Ziegler, J.; Nann, T. Rapid Synthesis of Highly Luminescent InP and InP/ZnS Nanocrystals. *J. Mater. Chem.* **2008**, *18*, 2653–2656.

(326) Gao, Y.; Peng, X. Photogenerated Excitons in Plain Core CdSe Nanocrystals with Unity Radiative Decay in Single Channel: The Effects of Surface and Ligands. *J. Am. Chem. Soc.* **2015**, *137*, 4230–4235.

(327) Pu, C.; Qin, H.; Gao, Y.; Zhou, J.; Wang, P.; Peng, X. Synthetic Control of Exciton Behavior in Colloidal Quantum Dots. *J. Am. Chem. Soc.* **2017**, *139*, 3302–3311.

(328) Pu, C.; Peng, X. To Battle Surface Traps on CdSe/CdS Core/Shell Nanocrystals: Shell Isolation *versus* Surface Treatment. *J. Am. Chem. Soc.* **2016**, *138*, 8134–8142.

(329) Dirin, D. N.; Protesescu, L.; Trummer, D.; Kochetygov, I. V.; Yakunin, S.; Krumeich, F.; Stadie, N. P.; Kovalenko, M. V. Harnessing Defect-Tolerance at the Nanoscale: Highly Luminescent Lead Halide Perovskite Nanocrystals in Mesoporous Silica Matrixes. *Nano Lett.* **2016**, *16*, 5866–5874.

(330) González-Carrero, S.; Martínez-Sarti, L.; Sessolo, M.; Galian, R. E.; Pérez-Prieto, J. Highly Photoluminescent, Dense Solid Films from Organic-Capped $\text{CH}_3\text{NH}_3\text{PbBr}_3$ Perovskite Colloids. *J. Mater. Chem. C* **2018**, *6*, 6771–6777.

(331) Kang, J.; Wang, L.-W. High Defect Tolerance in Lead Halide Perovskite CsPbBr_3 . *J. Phys. Chem. Lett.* **2017**, *8*, 489–493.

(332) Di Stasio, F.; Christodoulou, S.; Huo, N.; Konstantatos, G. Near-Unity Photoluminescence Quantum Yield in CsPbBr_3 Nano-

crystal Solid-State Films *via* Postsynthesis Treatment with Lead Bromide. *Chem. Mater.* **2017**, *29*, 7663–7667.

(333) Galian, R. E.; Pérez-Prieto, J. Synergism at the Nanoscale: Photoactive Semiconductor Nanoparticles and Their Organic Ligands. *Research Perspectives on Functional Micro- and Nanoscale Coatings*; IGI Global: Hershey, PA, 2016; pp 42–77.

(334) Pan, J.; Quan, L. N.; Zhao, Y.; Peng, W.; Murali, B.; Sarmah, S. P.; Yuan, M.; Sinatra, L.; Alyami, N. M.; Liu, J.; Yassitepe, E.; Yang, Z.; Voznyy, O.; Comin, R.; Hedhili, M. N.; Mohammed, O. F.; Lu, Z. H.; Kim, D. H.; Sargent, E. H.; Bakr, O. M. Highly Efficient Perovskite-Quantum-Dot Light-Emitting Diodes by Surface Engineering. *Adv. Mater.* **2016**, *28*, 8718–8725.

(335) Vickers, E. T.; Graham, T. A.; Chowdhury, A. H.; Bahrami, B.; Dreskin, B. W.; Lindley, S.; Naghadeh, S. B.; Qiao, Q.; Zhang, J. Z. Improving Charge Carrier Delocalization in Perovskite Quantum Dots by Surface Passivation with Conductive Aromatic Ligands. *ACS Energy Lett.* **2018**, *3*, 2931–2939.

(336) Anderson, N. C.; Hendricks, M. P.; Choi, J. J.; Owen, J. S. Ligand Exchange and the Stoichiometry of Metal Chalcogenide Nanocrystals: Spectroscopic Observation of Facile Metal-Carboxylate Displacement and Binding. *J. Am. Chem. Soc.* **2013**, *135*, 18536–18548.

(337) De Roo, J.; Yazdani, N.; Drijvers, E.; Lauria, A.; Maes, J.; Owen, J. S.; Van Driessche, I.; Niederberger, M.; Wood, V.; Martins, J. C.; Infante, I.; Hens, Z. Probing Solvent–Ligand Interactions in Colloidal Nanocrystals by the NMR Line Broadening. *Chem. Mater.* **2018**, *30*, 5485–5492.

(338) Moreels, I.; Fritzinger, B.; Martins, J. C.; Hens, Z. Surface Chemistry of Colloidal PbSe Nanocrystals. *J. Am. Chem. Soc.* **2008**, *130*, 15081–15086.

(339) Green, M. L. H. A New Approach to the Formal Classification of Covalent Compounds of the Elements. *J. Organomet. Chem.* **1995**, *500*, 127–148.

(340) Green, M. L. H.; Parkin, G. Application of the Covalent Bond Classification Method for the Teaching of Inorganic Chemistry. *J. Chem. Educ.* **2014**, *91*, 807–816.

(341) Gonzalez-Carrero, S.; Francés-Soriano, L.; González-Béjar, M.; Agouram, S.; Galian, R. E.; Pérez-Prieto, J. The Luminescence of $\text{CH}_3\text{NH}_3\text{PbBr}_3$ Perovskite Nanoparticles Crests the Summit and Their Photostability under Wet Conditions is Enhanced. *Small* **2016**, *12*, 5245–5250.

(342) Huang, H.; Raith, J.; Kershaw, S. V.; Kalytchuk, S.; Tomanec, O.; Jing, L.; Susha, A. S.; Zboril, R.; Rogach, A. L. Growth Mechanism of Strongly Emitting $\text{CH}_3\text{NH}_3\text{PbBr}_3$ Perovskite Nanocrystals with A Tunable Bandgap. *Nat. Commun.* **2017**, *8*, 996.

(343) McCleverty, J. A.; Meyer, T. J. *Comprehensive Coordination Chemistry II: From Biology to Nanotechnology*; Elsevier: Amsterdam, 2003; Vol. 2.

(344) Luo, B.; Pu, Y.-C.; Lindley, S. A.; Yang, Y.; Lu, L.; Li, Y.; Li, X.; Zhang, J. Z. Organolead Halide Perovskite Nanocrystals: Branched Capping Ligands Control Crystal Size and Stability. *Angew. Chem., Int. Ed.* **2016**, *55*, 8864–8868.

(345) Jancik Prochazkova, A.; Salinas, Y.; Yumusak, C.; Brüggemann, O.; Weiter, M.; Sariciftci, N. S.; Krajcovic, J.; Kovalenko, A. Cyclic Peptide Stabilized Lead Halide Perovskite Nanoparticles. *Sci. Rep.* **2019**, *9*, 12966.

(346) Yassitepe, E.; Yang, Z.; Voznyy, O.; Kim, Y.; Walters, G.; Castañeda, J. A.; Kanjanaboons, P.; Yuan, M.; Gong, X.; Fan, F.; Pan, J.; Hoogland, S.; Comin, R.; Bakr, O. M.; Padilha, L. A.; Nogueira, A. F.; Sargent, E. H. Amine-Free Synthesis of Cesium Lead Halide Perovskite Quantum Dots for Efficient Light-Emitting Diodes. *Adv. Funct. Mater.* **2016**, *26*, 8757–8763.

(347) Lu, H.; Zhu, X.; Miller, C.; San Martin, J.; Chen, X.; Miller, E. M.; Yan, Y.; Beard, M. C. Enhanced Photoredox Activity of CsPbBr_3 Nanocrystals by Quantitative Colloidal Ligand Exchange. *J. Chem. Phys.* **2019**, *151*, 204305.

(348) Rosa-Pardo, I.; Casadevall, C.; Schmidt, L.; Claros, M.; Galian, R. E.; Lloret-Fillol, J.; Pérez-Prieto, J. The Synergy Between the CsPbBr_3 Nanoparticle Surface and the Organic Ligand Becomes Manifest in a Demanding Carbon–Carbon Coupling Reaction. *Chem. Commun.* **2020**, *56*, 5026–5029.

(349) Ruan, L.; Shen, W.; Wang, A.; Xiang, A.; Deng, Z. Alkyl-Thiol Ligand-Induced Shape- and Crystalline Phase-Controlled Synthesis of Stable Perovskite-Related CsPb_2Br_5 Nanocrystals at Room Temperature. *J. Phys. Chem. Lett.* **2017**, *8*, 3853–3860.

(350) Ravi, V. K.; Santra, P. K.; Joshi, N.; Chugh, J.; Singh, S. K.; Rensmo, H.; Ghosh, P.; Nag, A. Origin of the Substitution Mechanism for the Binding of Organic Ligands on the Surface of CsPbBr_3 Perovskite Nanocubes. *J. Phys. Chem. Lett.* **2017**, *8*, 4988–4994.

(351) Zhang, B.; Goldoni, L.; Zito, J.; Dang, Z.; Almeida, G.; Zaccaria, F.; de Wit, J.; Infante, I.; De Trizio, L.; Manna, L. Alkyl Phosphonic Acids Deliver CsPbBr_3 Nanocrystals with High Photoluminescence Quantum Yield and Truncated Octahedron Shape. *Chem. Mater.* **2019**, *31*, 9140–9147.

(352) Yang, D.; Li, X.; Zhou, W.; Zhang, S.; Meng, C.; Wu, Y.; Wang, Y.; Zeng, H. CsPbBr_3 Quantum Dots 2.0: Benzenesulfonic Acid Equivalent Ligand Awakens Complete Purification. *Adv. Mater.* **2019**, *31*, 1900767.

(353) Huang, S.; Wang, B.; Zhang, Q.; Li, Z.; Shan, A.; Li, L. Postsynthesis Potassium-Modification Method to Improve Stability of CsPbBr_3 Perovskite Nanocrystals. *Adv. Opt. Mater.* **2018**, *6*, 1701106.

(354) Zhang, X.; Lv, L.; Ji, L.; Guo, G.; Liu, L.; Han, D.; Wang, B.; Tu, Y.; Hu, J.; Yang, D.; Dong, A. Self-Assembly of One-Dimensional Nanocrystal Superlattice Chains Mediated by Molecular Clusters. *J. Am. Chem. Soc.* **2016**, *138*, 3290–3293.

(355) Gonzalez-Carrero, S.; Bareño, L.; Debroye, E.; Martin, C.; Bondia, P.; Flors, C.; Galian, R. E.; Hofkens, J.; Pérez-Prieto, J. Linear Assembly of Lead Bromide-Based Nanoparticles Inside Lead(II) Polymers Prepared by Mixing the Precursors of Both the Nanoparticle and the Polymer. *Chem. Commun.* **2019**, *55*, 2968–2971.

(356) Zhang, J. Z. A “Cocktail” Approach to Effective Surface Passivation of Multiple Surface Defects of Metal Halide Perovskites Using a Combination of Ligands. *J. Phys. Chem. Lett.* **2019**, *10*, 5055–5063.

(357) Wang, S.; Zhou, L.; Huang, F.; Xin, Y.; Jin, P.; Ma, Q.; Pang, Q.; Chen, Y.; Zhang, J. Z. Hybrid Organic–Inorganic Lead Bromide Perovskite Supercrystals Self-Assembled with L-Cysteine and Their Good Luminescence Properties. *J. Mater. Chem. C* **2018**, *6*, 10994–11001.

(358) Hu, Y.; Zhang, X.; Yang, C.; Li, J.; Wang, L. Fe^{2+} Doped in CsPbCl_3 Perovskite Nanocrystals: Impact on the Luminescence and Magnetic Properties. *RSC Adv.* **2019**, *9*, 33017–33022.

(359) Wang, F.; Geng, W.; Zhou, Y.; Fang, H. H.; Tong, C. J.; Loi, M. A.; Liu, L. M.; Zhao, N. Phenylalkylamine Passivation of Organolead Halide Perovskites Enabling High-Efficiency and Air-Stable Photovoltaic Cells. *Adv. Mater.* **2016**, *28*, 9986–9992.

(360) Xu, K.; Vickers, E. T.; Rao, L.; Lindley, S. A.; Allen, A. C.; Luo, B.; Li, X.; Zhang, J. Z. Synergistic Surface Passivation of $\text{CH}_3\text{NH}_3\text{PbBr}_3$ Perovskite Quantum Dots with Phosphonic Acid and (3-Aminopropyl)triethoxysilane. *Chem. - Eur. J.* **2019**, *25*, 5014–5021.

(361) Zhang, Z.; Li, X.; Xia, X.; Wang, Z.; Huang, Z.; Lei, B.; Gao, Y. High-Quality $(\text{CH}_3\text{NH}_3)_3\text{Bi}_2\text{I}_9$ Film-Based Solar Cells: Pushing Efficiency up to 1.64. *J. Phys. Chem. Lett.* **2017**, *8*, 4300–4307.

(362) Wei, J.; Huang, F.; Wang, S.; Zhou, L.; Xin, Y.; Jin, P.; Cai, Z.; Yin, Z.; Pang, Q.; Zhang, J. Z. Highly Stable and Efficient Hybrid Perovskite Solar Cells Improved with Conductive Polyanilines. *Mater. Res. Bull.* **2018**, *106*, 35–39.

(363) Luo, B.; Naghadeh, S. B.; Allen, A. L.; Li, X.; Zhang, J. Z. Peptide-Passivated Lead Halide Perovskite Nanocrystals Based on Synergistic Effect between Amino and Carboxylic Functional Groups. *Adv. Funct. Mater.* **2017**, *27*, 1604018.

(364) Wang, Y.; Yu, D.; Wang, Z.; Li, X.; Chen, X.; Nalla, V.; Zeng, H.; Sun, H. Solution-Grown $\text{CsPbBr}_3/\text{Cs}_4\text{PbBr}_6$ Perovskite Nanocomposites: Toward Temperature-Insensitive Optical Gain. *Small* **2017**, *13*, 1701587.

(365) Li, Z. J.; Hofman, E.; Li, J.; Davis, A. H.; Tung, C. H.; Wu, L. Z.; Zheng, W. Photoelectrochemically Active and Environmentally

Stable $\text{CsPbBr}_3/\text{TiO}_2$ Core/Shell Nanocrystals. *Adv. Funct. Mater.* **2018**, *28*, 1704288.

(366) Inglezakis, V. J.; Loizidou, M. D.; Grigoropoulou, H. P. Ion Exchange of Pb^{2+} , Cu^{2+} , Fe^{3+} , and Cr^{3+} on Natural Clinoptilolite: Selectivity Determination and Influence of Acidity on Metal Uptake. *J. Colloid Interface Sci.* **2003**, *261*, 49–54.

(367) Li, C.; Yin, J.; Chen, R.; Lv, X.; Feng, X.; Wu, Y.; Cao, J. Monoammonium Porphyrin for Blade-Coating Stable Large-Area Perovskite Solar Cells with >18% Efficiency. *J. Am. Chem. Soc.* **2019**, *141*, 6345–6351.

(368) Xu, K.; Allen, A. C.; Luo, B.; Vickers, E. T.; Wang, Q.; Hollingsworth, W. R.; Ayzner, A. L.; Li, X.; Zhang, J. Z. Tuning from Quantum Dots to Magic Sized Clusters of CsPbBr_3 Using Novel Planar Ligands Based on Trivalent Nitrate Coordination Complex. *J. Phys. Chem. Lett.* **2019**, *10*, 4409–4416.

(369) Dai, J.; Xi, J.; Li, L.; Zhao, J.; Shi, Y.; Zhang, W.; Ran, C.; Jiao, B.; Hou, X.; Duan, X.; Wu, Z. Charge Transport between Coupling Colloidal Perovskite Quantum Dots Assisted by Functional Conjugated Ligands. *Angew. Chem., Int. Ed.* **2018**, *57*, 5754–5758.

(370) Li, X.; Ibrahim Dar, M.; Yi, C.; Luo, J.; Tschumi, M.; Zakeeruddin, S. M.; Nazeeruddin, M. K.; Han, H.; Gratzel, M. Improved Performance and Stability of Perovskite Solar Cells by Crystal Crosslinking with Alkylphosphonic Acid Omega-Ammonium Chlorides. *Nat. Chem.* **2015**, *7*, 703–711.

(371) Wei, J.; Huang, F.; Wang, S.; Zhou, L.; Jin, P.; Xin, Y.; Cai, Z.; Yin, Z.; Pang, Q.; Zhang, J. Z. Highly Stable Hybrid Perovskite Solar Cells Modified with Polyethylenimine via Ionic Bonding. *Chem-NanoMat* **2018**, *4*, 649–655.

(372) Rao, L.; Ding, X.; Du, X.; Liang, G.; Tang, Y.; Tang, K.; Zhang, J. Z. Ultrasonication-Assisted Synthesis of CsPbBr_3 and Cs_4PbBr_6 Perovskite Nanocrystals and Their Reversible Transformation. *Beilstein J. Nanotechnol.* **2019**, *10*, 666–676.

(373) Zhu, J.; Zhu, Y.; Huang, J.; Gong, Y.; Shen, J.; Li, C. Synthesis of CsPbBr_3 Perovskite Nanocrystals With the Sole Ligand of Protonated (3-aminopropyl)triethoxysilane. *J. Mater. Chem. C* **2019**, *7*, 7201–7206.

(374) Abdelfageed, G.; Sully, H. R.; Bonabi Naghadeh, S.; El-Hag Ali, A.; Carter, S. A.; Zhang, J. Z. Improved Stability of Organometal Halide Perovskite Films and Solar Cells toward Humidity via Surface Passivation with Oleic Acid. *ACS Appl. Energy Mater.* **2018**, *1*, 387–392.

(375) Vickers, E. T.; Xu, K.; Dreskin, B. W.; Graham, T. A.; Li, X.; Zhang, J. Z. Ligand Dependent Growth and Optical Properties of Hybrid Organo-metal Halide Perovskite Magic Sized Clusters. *J. Phys. Chem. C* **2019**, *123*, 18746–18752.

(376) Zhong, Y.; Munir, R.; Balawi, A. H.; Sheikh, A. D.; Yu, L.; Tang, M.-C.; Hu, H.; Laquai, F.; Amassian, A. Mesostructured Fullerene Electrodes for Highly Efficient $n-i-p$ Perovskite Solar Cells. *ACS Energy Lett.* **2016**, *1*, 1049–1056.

(377) Dong, H.; Xi, J.; Zuo, L.; Li, J.; Yang, Y.; Wang, D.; Yu, Y.; Ma, L.; Ran, C.; Gao, W.; Jiao, B.; Xu, J.; Lei, T.; Wei, F.; Yuan, F.; Zhang, L.; Shi, Y.; Hou, X.; Wu, Z. Conjugated Molecules “Bridge”: Functional Ligand toward Highly Efficient and Long-Term Stable Perovskite Solar Cell. *Adv. Funct. Mater.* **2019**, *29*, 1808119.

(378) Nevers, D. R.; Williamson, C. B.; Savitzky, B. H.; Hadar, I.; Banin, U.; Kourkoutis, L. F.; Hanrath, T.; Robinson, R. D. Mesophase Formation Stabilizes High-Purity Magic-Sized Clusters. *J. Am. Chem. Soc.* **2018**, *140*, 3652–3662.

(379) Evans, C. M.; Love, A. M.; Weiss, E. A. Surfactant-Controlled Polymerization of Semiconductor Clusters to Quantum Dots through Competing Step-Growth and Living Chain-Growth Mechanisms. *J. Am. Chem. Soc.* **2012**, *134*, 17298–17305.

(380) Yu, K. Cdse Magic-Sized Nuclei, Magic-Sized Nanoclusters and Regular Nanocrystals: Monomer Effects on Nucleation And Growth. *Adv. Mater.* **2012**, *24*, 1123–1132.

(381) Peng, L.; Geng, J.; Ai, L.; Zhang, Y.; Xie, R.; Yang, W. Room Temperature Synthesis of Ultra-Small, Near-Unity Single-Sized Lead Halide Perovskite Quantum Dots with Wide Color Emission Tunability, High Color Purity And High Brightness. *Nanotechnology* **2016**, *27*, 335604.

(382) Xu, Y.; Zhang, Q.; Lv, L.; Han, W.; Wu, G.; Yang, D.; Dong, A. Synthesis of Ultrasmall CsPbBr_3 Nanoclusters and Their Transformation to Highly Deep-Blue-Emitting Nanoribbons At Room Temperature. *Nanoscale* **2017**, *9*, 17248–17253.

(383) Zheng, W.; Li, Z.; Zhang, C.; Wang, B.; Zhang, Q.; Wan, Q.; Kong, L.; Li, L. Stabilizing Perovskite Nanocrystals by Controlling Protective Surface Ligands Density. *Nano Res.* **2019**, *12*, 1461–1465.

(384) Quarta, D.; Imran, M.; Capodilupo, A.-L.; Petralanda, U.; van Beek, B.; De Angelis, F.; Manna, L.; Infante, I.; De Trizio, L.; Giansante, C. Stable Ligand Coordination at the Surface of Colloidal CsPbBr_3 Nanocrystals. *J. Phys. Chem. Lett.* **2019**, *10*, 3715–3726.

(385) Wang, N.; Cheng, L.; Ge, R.; Zhang, S.; Miao, Y.; Zou, W.; Yi, C.; Sun, Y.; Cao, Y.; Yang, R.; Wei, Y.; Guo, Q.; Ke, Y.; Yu, M.; Jin, Y.; Liu, Y.; Ding, Q.; Di, D.; Yang, L.; Xing, G.; Tian, H.; Jin, C.; Gao, F.; Friend, R. H.; Wang, J.; Huang, W. Perovskite Light-Emitting Diodes Based on Solution-Processed Self-Organized Multiple Quantum Wells. *Nat. Photonics* **2016**, *10*, 699–704.

(386) Long, Z.; Wang, Y.; Fu, Q.; Ouyang, J.; He, L.; Na, N. Accelerated Crystallization and Encapsulation for the Synthesis of Water- and Oxygen-Resistant Perovskite Nanoparticles in Micro-Droplets. *Nanoscale* **2019**, *11*, 11093–11098.

(387) Gautier, R.; Paris, M.; Massuyeau, F. Exciton Self-Trapping in Hybrid Lead Halides: Role of Halogen. *J. Am. Chem. Soc.* **2019**, *141*, 12619–12623.

(388) Pan, J.; Quan, L. N.; Zhao, Y.; Peng, W.; Murali, B.; Sarmah, S. P.; Yuan, M.; Sinatra, L.; Alyami, N. M.; Liu, J.; Yassitepe, E.; Yang, Z.; Voznyy, O.; Comin, R.; Hedhili, M. N.; Mohammed, O. F.; Lu, Z. H.; Kim, D. H.; Sargent, E. H.; Bakr, O. M. Highly Efficient Perovskite-Quantum-Dot Light-Emitting Diodes by Surface Engineering. *Adv. Mater.* **2016**, *28*, 8718–8725.

(389) Pan, J.; Sarmah, S. P.; Murali, B.; Dursun, I.; Peng, W.; Parida, M. R.; Liu, J.; Sinatra, L.; Alyami, N.; Zhao, C.; Alarousu, E.; Ng, T. K.; Ooi, B. S.; Bakr, O. M.; Mohammed, O. F. Air-Stable Surface-Passivated Perovskite Quantum Dots for Ultra-Robust, Single- and Two-Photon-Induced Amplified Spontaneous Emission. *J. Phys. Chem. Lett.* **2015**, *6*, 5027–5033.

(390) Ahmed, T.; Seth, S.; Samanta, A. Boosting the Photoluminescence of CsPbX_3 ($X = \text{Cl}, \text{Br}, \text{I}$) Perovskite Nanocrystals Covering a Wide Wavelength Range by Postsynthetic Treatment with Tetrafluoroborate Salts. *Chem. Mater.* **2018**, *30*, 3633–3637.

(391) Ahmed, G. H.; El-Demellawi, J. K.; Yin, J.; Pan, J.; Velusamy, D. B.; Hedhili, M. N.; Alarousu, E.; Bakr, O. M.; Alshareef, H. N.; Mohammed, O. F. Giant Photoluminescence Enhancement in CsPbCl_3 Perovskite Nanocrystals by Simultaneous Dual-Surface Passivation. *ACS Energy Lett.* **2018**, *3*, 2301–2307.

(392) Yang, D.; Li, X.; Wu, Y.; Wei, C.; Qin, Z.; Zhang, C.; Sun, Z.; Li, Y.; Wang, Y.; Zeng, H. Surface Halogen Compensation for Robust Performance Enhancements of CsPbX_3 Perovskite Quantum Dots. *Adv. Opt. Mater.* **2019**, *7*, 1900276.

(393) Xie, R.; Rutherford, M.; Peng, X. Formation of High-Quality I–III–VI Semiconductor Nanocrystals by Tuning Relative Reactivity of Cationic Precursors. *J. Am. Chem. Soc.* **2009**, *131*, 5691–5697.

(394) Li, L. S.; Pradhan, N.; Wang, Y.; Peng, X. High Quality ZnSe and ZnS Nanocrystals Formed by Activating Zinc Carboxylate Precursors. *Nano Lett.* **2004**, *4*, 2261–2264.

(395) Li, Z.; Ji, Y.; Xie, R.; Grisham, S. Y.; Peng, X. Correlation of CdS Nanocrystal Formation with Elemental Sulfur Activation and Its Implication in Synthetic Development. *J. Am. Chem. Soc.* **2011**, *133*, 17248–17256.

(396) Song, J.; Fang, T.; Li, J.; Xu, L.; Zhang, F.; Han, B.; Shan, Q.; Zeng, H. Organic–Inorganic Hybrid Passivation Enables Perovskite QLEDs with an EQE of 16.48%. *Adv. Mater.* **2018**, *30*, 1805409.

(397) Woo, J. Y.; Kim, Y.; Bae, J.; Kim, T. G.; Kim, J. W.; Lee, D. C.; Jeong, S. Highly Stable Cesium Lead Halide Perovskite Nanocrystals through *in Situ* Lead Halide Inorganic Passivation. *Chem. Mater.* **2017**, *29*, 7088–7092.

(398) Wu, Y.; Wei, C.; Li, X.; Li, Y.; Qiu, S.; Shen, W.; Cai, B.; Sun, Z.; Yang, D.; Deng, Z.; Zeng, H. *In Situ* Passivation of PbBr_6^{4-} Octahedra toward Blue Luminescent CsPbBr_3 Nanoplatelets with Near 100% Absolute Quantum Yield. *ACS Energy Letters* **2018**, *3*, 2030–2037.

(399) Yong, Z.-J.; Guo, S.-Q.; Ma, J.-P.; Zhang, J.-Y.; Li, Z.-Y.; Chen, Y.-M.; Zhang, B.-B.; Zhou, Y.; Shu, J.; Gu, J.-L.; Zheng, L.-R.; Bakr, O. M.; Sun, H.-T. Doping-Enhanced Short-Range Order of Perovskite Nanocrystals for Near-Unity Violet Luminescence Quantum Yield. *J. Am. Chem. Soc.* **2018**, *140*, 9942–9951.

(400) Yang, J.-N.; Song, Y.; Yao, J.-S.; Wang, K.-H.; Wang, J.-J.; Zhu, B.-S.; Yao, M.-M.; Rahman, S. U.; Lan, Y.-F.; Fan, F.-J.; Yao, H.-B. Potassium-Bromide Surface Passivation on $\text{CsPbI}_{3-x}\text{Br}_x$ Nanocrystals for Efficient and Stable Pure Red Perovskite Light Emitting Diodes. *J. Am. Chem. Soc.* **2020**, *142*, 2956–2967.

(401) Wu, H.; Zhang, Y.; Lu, M.; Zhang, X.; Sun, C.; Zhang, T.; Colvin, V. L.; Yu, W. W. Surface Ligand Modification of Cesium Lead Bromide Nanocrystals for Improved Light-Emitting Performance. *Nanoscale* **2018**, *10*, 4173–4178.

(402) Luo, C.; Li, W.; Xiong, D.; Fu, J.; Yang, W. Surface Pre-Optimization of A Mixed Halide Perovskite toward High Photoluminescence Quantum Yield in the Blue Spectrum Range. *Nanoscale* **2019**, *11*, 15206–15215.

(403) Kim, Y.-H.; Lee, G.-H.; Kim, Y.-T.; Wolf, C.; Yun, H. J.; Kwon, W.; Park, C. G.; Lee, T. W. High Efficiency Perovskite Light-Emitting Diodes of Ligand-Engineered Colloidal Formamidinium Lead Bromide Nanoparticles. *Nano Energy* **2017**, *38*, 51–58.

(404) Lin, K.; Xing, J.; Quan, L. N.; de Arquer, F. P. G.; Gong, X.; Lu, J.; Xie, L.; Zhao, W.; Zhang, D.; Yan, C.; Li, W.; Liu, X.; Lu, Y.; Kirman, J.; Sargent, E. H.; Xiong, Q.; Wei, Z. Perovskite Light-Emitting Diodes with External Quantum Efficiency Exceeding 20 Per Cent. *Nature* **2018**, *562*, 245–248.

(405) Lu, M.; Guo, J.; Sun, S.; Lu, P.; Zhang, X.; Shi, Z.; Yu, W. W.; Zhang, Y. Surface Ligand Engineering-Assisted CsPbI_3 Quantum Dots Enable Bright and Efficient Red Light-Emitting Diodes with A Top-Emitting Structure. *Chem. Eng. J.* **2021**, *404*, 126563.

(406) Park, J. H.; Lee, A.-y.; Yu, J. C.; Nam, Y. S.; Choi, Y.; Park, J.; Song, M. H. Surface Ligand Engineering for Efficient Perovskite Nanocrystal-Based Light-Emitting Diodes. *ACS Appl. Mater. Interfaces* **2019**, *11*, 8428–8435.

(407) Yan, W.; Shen, J.; Zhu, Y.; Gong, Y.; Zhu, J.; Wen, Z.; Li, C. CsPbBr_3 Quantum Dots Photodetectors Boosting Carrier Transport via Molecular Engineering Strategy. *Nano Res.* **2021**, DOI: 10.1007/s12274-021-3333-z.

(408) Hassan, Y.; Park, J. H.; Crawford, M. L.; Sadhanala, A.; Lee, J.; Sadighian, J. C.; Mosconi, E.; Shivanna, R.; Radicchi, E.; Jeong, M.; Yang, C.; Choi, H.; Park, S. H.; Song, M. H.; De Angelis, F.; Wong, C. Y.; Friend, R. H.; Lee, B. R.; Snaith, H. J. Ligand-Engineered Bandgap Stability in Mixed-Halide Perovskite LEDs. *Nature* **2021**, *591*, 72–77.

(409) Han, B.; Yuan, S.; Fang, T.; Zhang, F.; Shi, Z.; Song, J. Novel Lewis Base Cyclam Self-Passivation of Perovskites without an Anti-Solvent Process for Efficient Light-Emitting Diodes. *ACS Appl. Mater. Interfaces* **2020**, *12*, 14224–14232.

(410) Saidaminov, M. I.; Almutlaq, J.; Sarmah, S.; Dursun, I.; Zhumekeenov, A. A.; Begum, R.; Pan, J.; Cho, N.; Mohammed, O. F.; Bakr, O. M. Pure Cs_4PbBr_6 : Highly Luminescent Zero Dimensional Perovskite Solids. *ACS Energy Lett.* **2016**, *1*, 840–845.

(411) Akkerman, Q. A.; Park, S.; Radicchi, E.; Nunzi, F.; Mosconi, E.; De Angelis, F.; Brescia, R.; Rastogi, P.; Prato, M.; Manna, L. Nearly Monodisperse Insulator Cs_4PbX_6 ($X = \text{Cl}, \text{Br}, \text{I}$) Nanocrystals, Their Mixed Halide Compositions, and Their Transformation into CsPbX_3 Nanocrystals. *Nano Lett.* **2017**, *17*, 1924–1930.

(412) Seth, S.; Samanta, A. Fluorescent Phase-Pure Zero-Dimensional Perovskite-Related Cs_4PbBr_6 Microdisks: Synthesis and Single-Particle Imaging Study. *J. Phys. Chem. Lett.* **2017**, *8*, 4461–4467.

(413) Zhang, Y. H.; Saidaminov, M. I.; Dursun, I.; Yang, H. Z.; Murali, B.; Alarousu, E.; Yengel, E.; Alshankiti, B. A.; Bakr, O. M.; Mohammed, O. F. Zero-Dimensional Cs_4PbBr_6 Perovskite Nanocrystals. *J. Phys. Chem. Lett.* **2017**, *8*, 961–965.

(414) Mohammed, O. F. Outstanding Challenges of Zero-Dimensional Perovskite Materials. *J. Phys. Chem. Lett.* **2019**, *10*, 5886–5888.

(415) Thumu, U.; Piotrowski, M.; Owens-Baird, B.; Kolen'ko, Y. V. Zero-Dimensional Cesium Lead Halide Perovskites: Phase Transformations, Hybrid Structures, and Applications. *J. Solid State Chem.* **2019**, *271*, 361–377.

(416) Udayabaskararao, T.; Houben, L.; Cohen, H.; Menahem, M.; Pinkas, I.; Avram, L.; Wolf, T.; Teitelboim, A.; Leskes, M.; Yaffe, O.; Oron, D.; Kazes, M. A Mechanistic Study of Phase Transformation in Perovskite Nanocrystals Driven by Ligand Passivation. *Chem. Mater.* **2018**, *30*, 84–93.

(417) Wu, L. Z.; Hu, H. C.; Xu, Y.; Jiang, S.; Chen, M.; Zhong, Q. X.; Yang, D.; Liu, Q. P.; Zhao, Y.; Sun, B. Q.; Zhang, Q.; Yin, Y. D. From Nonluminescent Cs_4PbX_6 ($X = \text{Cl}, \text{Br}, \text{I}$) Nanocrystals to Highly Luminescent CsPbX_3 Nanocrystals: Water-Triggered Transformation through a CsX -Stripping Mechanism. *Nano Lett.* **2017**, *17*, 5799–5804.

(418) Zhang, Y.; Sinatra, L.; Alarousu, E.; Yin, J.; El-Zohry, A. M.; Bakr, O. M.; Mohammed, O. F. Ligand-Free Nanocrystals of Highly Emissive Cs_4PbBr_6 Perovskite. *J. Phys. Chem. C* **2018**, *122*, 6493–6498.

(419) Hui, J.; Jiang, Y. N.; Gokcinar, O. O.; Tang, J. B.; Yu, Q. Y.; Zhang, M.; Yu, K. Unveiling the Two-Step Formation Pathway of Cs_4PbBr_6 Nanocrystals. *Chem. Mater.* **2020**, *32*, 4574–4583.

(420) Li, Y. X.; Huang, H.; Xiong, Y.; Kershaw, S. V.; Rogach, A. L. Reversible Transformation Between CsPbBr_3 and Cs_4PbBr_6 Nanocrystals. *CrystEngComm* **2018**, *20*, 4900–4904.

(421) Liu, Z. K.; Bekenstein, Y.; Ye, X. C.; Nguyen, S. C.; Swabeck, J.; Zhang, D. D.; Lee, S. T.; Yang, P. D.; Ma, W. L.; Alivisatos, A. P. Ligand Mediated Transformation of Cesium Lead Bromide Perovskite Nanocrystals to Lead Depleted Cs_4PbBr_6 Nanocrystals. *J. Am. Chem. Soc.* **2017**, *139*, 5309–5312.

(422) Palazon, F.; Almeida, G.; Akkerman, Q. A.; De Trizio, L.; Dang, Z. Y.; Prato, M.; Manna, L. Changing the Dimensionality of Cesium Lead Bromide Nanocrystals by Reversible Postsynthesis Transformations with Amines. *Chem. Mater.* **2017**, *29*, 4167–4171.

(423) Palazon, F.; Urso, C.; De Trizio, L.; Akkerman, Q.; Marras, S.; Locardi, F.; Nelli, I.; Ferretti, M.; Prato, M.; Manna, L. Postsynthesis Transformation of Insulating Cs_4PbBr_6 Nanocrystals into Bright Perovskite CsPbBr_3 through Physical and Chemical Extraction of CsBr . *ACS Energy Lett.* **2017**, *2*, 2445–2448.

(424) Baranov, D.; Caputo, G.; Goldoni, L.; Dang, Z. Y.; Scarfiello, R. S.; De Trizio, L.; Portone, A.; Fabbri, F.; Camposeo, A.; Pisignano, D.; Manna, L. Transforming Colloidal Cs_4PbBr_6 Nanocrystals with Poly(Maleic Anhydride-Alt-1-Octadecene) into Stable CsPbBr_3 Perovskite Emitters through Intermediate Heterostructures. *Chem. Sci.* **2020**, *11*, 3986–3995.

(425) Yin, J.; Zhang, Y. H.; Bruno, A.; Soci, C.; Bakr, O. M.; Bredas, J. L.; Mohammed, O. F. Intrinsic Lead Ion Emissions in Zero-Dimensional Cs_4PbBr_6 Nanocrystals. *ACS Energy Lett.* **2017**, *2*, 2805–2811.

(426) Yin, J.; Maity, P.; De Bastiani, M.; Dursun, I.; Bakr, O. M.; Bredas, J. L.; Mohammed, O. F. Molecular Behavior of Zero-Dimensional Perovskites. *Sci. Adv.* **2017**, *3*, e1701793.

(427) Zhang, Y. H.; Guo, T. L.; Yang, H. Z.; Bose, R.; Liu, L. M.; Yin, J.; Han, Y.; Bakr, O. M.; Mohammed, O. F.; Malko, A. V. Emergence of Multiple Fluorophores in Individual Cesium Lead Bromide Nanocrystals. *Nat. Commun.* **2019**, *10*, 2930.

(428) Arunkumar, P.; Cho, H. B.; Gil, K. H.; Unithrattil, S.; Kim, Y. H.; Bin Im, W. Probing Molecule-Like Isolated Octahedra via-Phase Stabilization of Zero-Dimensional Cesium Lead Halide Nanocrystals. *Nat. Commun.* **2018**, *9*, 4691.

(429) Zou, S. H.; Liu, C. P.; Li, R. F.; Jiang, F. L.; Chen, X. Y.; Liu, Y. S.; Hong, M. C. From Nonluminescent to Blue-Emitting Cs_4PbBr_6 Nanocrystals: Tailoring the Insulator Bandgap of 0D Perovskite through Sn Cation Doping. *Adv. Mater.* **2019**, *31*, 1900606.

(430) Quan, L. N.; Quintero-Bermudez, R.; Voznyy, O.; Walters, G.; Jain, A.; Fan, J. Z.; Zheng, X. L.; Yang, Z. Y.; Sargent, E. H. Highly

Emissive Green Perovskite Nanocrystals in a Solid State Crystalline Matrix. *Adv. Mater.* **2017**, *29*, 1605945.

(431) Qin, Z. J.; Dai, S. Y.; Hadjiev, V. G.; Wang, C.; Xie, L. X.; Ni, Y. Z.; Wu, C. Z.; Yang, G.; Chen, S.; Deng, L. Z.; Yu, Q. K.; Feng, G. Y.; Wang, Z. M. M.; Bao, J. M. Revealing the Origin of Luminescence Center in 0D Cs_4PbBr_6 Perovskite. *Chem. Mater.* **2019**, *31*, 9098–9104.

(432) Riesen, N.; Lockrey, M.; Badek, K.; Riesen, H. On the Origins of the Green Luminescence In The "Zero-Dimensional Perovskite" Cs_4PbBr_6 : Conclusive Results from Cathodoluminescence Imaging. *Nanoscale* **2019**, *11*, 3925–3932.

(433) Yin, J.; Yang, H.; Song, K.; El-Zohry, A. M.; Han, Y.; Bakr, O. M.; Bredas, J. L.; Mohammed, O. F. Point Defects and Green Emission in Zero-Dimensional Perovskites. *J. Phys. Chem. Lett.* **2018**, *9*, 5490–5495.

(434) Cha, J. H.; Lee, H. J.; Kim, S. H.; Ko, K. C.; Suh, B. J.; Han, O. H.; Jung, D. Y. Superparamagnetism of Green Emissive Cs_4PbBr_6 Zero-Dimensional Perovskite Crystals. *ACS Energy Lett.* **2020**, *5*, 2208–2216.

(435) Jung, Y. K.; Calbo, J.; Park, J. S.; Whalley, L. D.; Kim, S.; Walsh, A. Intrinsic Doping Limit And Defect-Assisted Luminescence In Cs_4PbBr_6 . *J. Mater. Chem. A* **2019**, *7*, 20254–20261.

(436) Ray, A.; Maggioni, D.; Baranov, D.; Dang, Z. Y.; Prato, M.; Akkerman, Q. A.; Goldoni, L.; Caneva, E.; Manna, L.; Abdelhady, A. L. Green-Emitting Powders of Zero-Dimensional Cs_4PbBr_6 : Delineating the Intricacies of the Synthesis and the Origin of Photoluminescence. *Chem. Mater.* **2019**, *31*, 7761–7769.

(437) Bao, Z.; Wang, H. C.; Jiang, Z. F.; Chung, R. J.; Liu, R. S. Continuous Synthesis of Highly Stable Cs_4PbBr_6 Perovskite Microcrystals by a Microfluidic System and Their Application in White-Light-Emitting Diodes. *Inorg. Chem.* **2018**, *57*, 13071–13074.

(438) Sun, X.; Gao, Z.; Liu, Y.; Wang, Z.; Wang, X.; Zhang, W.; Xu, B.; Meng, X. Lasing from Zero-Dimensional Perovskite and Optical Imaging Applications. *ACS Photonics* **2019**, *6*, 3290–3297.

(439) Zhao, H. G.; Sun, R. J.; Wang, Z. F.; Fu, K. F.; Hu, X.; Zhang, Y. H. Zero-Dimensional Perovskite Nanocrystals for Efficient Luminescent Solar Concentrators. *Adv. Funct. Mater.* **2019**, *29*, 1902262.

(440) Seth, S.; Samanta, A. Photoluminescence of Zero-Dimensional Perovskites and Perovskite-Related Materials. *J. Phys. Chem. Lett.* **2018**, *9*, 176–183.

(441) Pan, A.; Jurow, M. J.; Qiu, F.; Yang, J.; Ren, B.; Urban, J. J.; He, L.; Liu, Y. Nanorod Suprastructures from a Ternary Graphene Oxide–Polymer– CsPbX_3 Perovskite Nanocrystal Composite That Display High Environmental Stability. *Nano Lett.* **2017**, *17*, 6759–6765.

(442) Zhang, H.; Wang, X.; Liao, Q.; Xu, Z.; Li, H.; Zheng, L.; Fu, H. Embedding Perovskite Nanocrystals into a Polymer Matrix for Tunable Luminescence Probes in Cell Imaging. *Adv. Funct. Mater.* **2017**, *27*, 1604382.

(443) Yoon, H. C.; Lee, H.; Kang, H.; Oh, J. H.; Do, Y. R. Highly Efficient Wide-Color-Gamut QD-Emissive LCDs Using Red and Green Perovskite Core/Shell QDs. *J. Mater. Chem. C* **2018**, *6*, 13023–13033.

(444) Wang, H.-C.; Lin, S.-Y.; Tang, A.-C.; Singh, B. P.; Tong, H.-C.; Chen, C.-Y.; Lee, Y.-C.; Tsai, T.-L.; Liu, R.-S. Mesoporous Silica Particles Integrated with All-Inorganic CsPbBr_3 Perovskite Quantum-Dot Nanocomposites (MP-PQDs) with High Stability and Wide Color Gamut Used for Backlight Display. *Angew. Chem., Int. Ed.* **2016**, *55*, 7924–7929.

(445) Sun, C.; Zhang, Y.; Ruan, C.; Yin, C.; Wang, X.; Wang, Y.; Yu, W. W. Efficient and Stable White LEDs with Silica-Coated Inorganic Perovskite Quantum Dots. *Adv. Mater.* **2016**, *28*, 10088–10094.

(446) Li, Z.; Kong, L.; Huang, S.; Li, L. Highly Luminescent and Ultrastable CsPbBr_3 Perovskite Quantum Dots Incorporated into a Silica/Alumina Monolith. *Angew. Chem., Int. Ed.* **2017**, *56*, 8134–8138.

(447) Xu, K.; Lin, C. C.; Xie, X.; Meijerink, A. Efficient and Stable Luminescence from Mn^{2+} in Core and Core–Isocrystalline Shell CsPbCl₃ Perovskite Nanocrystals. *Chem. Mater.* **2017**, *29*, 4265–4272.

(448) Wang, S.; Bi, C.; Yuan, J.; Zhang, L.; Tian, J. Original Core–Shell Structure of Cubic CsPbBr_3 @Amorphous CsPbBr_x Perovskite Quantum Dots with a High Blue Photoluminescence Quantum Yield of over 80%. *ACS Energy Lett.* **2018**, *3*, 245–251.

(449) Moot, T.; Dikova, D. R.; Hazarika, A.; Schloemer, T. H.; Habisreutinger, S. N.; Leick, N.; Dunfield, S. P.; Rosales, B. A.; Harvey, S. P.; Pfeilsticker, J. R.; Teeter, G.; Wheeler, L. M.; Larson, B. W.; Luther, J. M. Beyond Strain: Controlling the Surface Chemistry of CsPbI_3 Nanocrystal Films for Improved Stability against Ambient Reactive Oxygen Species. *Chem. Mater.* **2020**, *32*, 7850–7860.

(450) Xuan, T.; Lou, S.; Huang, J.; Cao, L.; Yang, X.; Li, H.; Wang, J. Monodisperse and Brightly Luminescent $\text{CsPbBr}_3/\text{Cs}_4\text{PbBr}_6$ Perovskite Composite Nanocrystals. *Nanoscale* **2018**, *10*, 9840–9844.

(451) Xu, J.; Huang, W.; Li, P.; Onken, D. R.; Dun, C.; Guo, Y.; Ucer, K. B.; Lu, C.; Wang, H.; Geyer, S. M.; Williams, R. T.; Carroll, D. L. Imbedded Nanocrystals of CsPbBr_3 in Cs_4PbBr_6 : Kinetics, Enhanced Oscillator Strength, and Application in Light-Emitting Diodes. *Adv. Mater.* **2017**, *29*, 1703703.

(452) Chen, X.; Zhang, F.; Ge, Y.; Shi, L.; Huang, S.; Tang, J.; Lv, Z.; Zhang, L.; Zou, B.; Zhong, H. Centimeter-Sized Cs_4PbBr_6 Crystals with Embedded CsPbBr_3 Nanocrystals Showing Superior Photoluminescence: Nonstoichiometry Induced Transformation and Light-Emitting Applications. *Adv. Funct. Mater.* **2018**, *28*, 1706567.

(453) Selvan, S. T.; Tan, T. T.; Ying, J. Y. Robust, Non-Cytotoxic, Silica-Coated CdSe Quantum Dots with Efficient Photoluminescence. *Adv. Mater.* **2005**, *17*, 1620–1625.

(454) Zhang, T.; Stilwell, J. L.; Gerion, D.; Ding, L.; Elboudwarej, O.; Cooke, P. A.; Gray, J. W.; Alivisatos, A. P.; Chen, F. F. Cellular Effect of High Doses of Silica-Coated Quantum Dot Profiled with High Throughput Gene Expression Analysis and High Content Cellomics Measurements. *Nano Lett.* **2006**, *6*, 800–808.

(455) Gao, F.; Yang, W.; Liu, X.; Li, Y.; Liu, W.; Xu, H.; Liu, Y. Highly Stable and Luminescent Silica-Coated Perovskite Quantum Dots at Nanoscale-Particle Level *via* Nonpolar Solvent Synthesis. *Chem. Eng. J.* **2021**, *407*, 128001.

(456) Meng, C.; Yang, D.; Wu, Y.; Zhang, X.; Zeng, H.; Li, X. Synthesis of Single $\text{CsPbBr}_3@\text{SiO}_2$ Core–Shell Particles *via* Surface Activation. *J. Mater. Chem. C* **2020**, *8*, 17403–17409.

(457) Yang, W.; Gao, F.; Qiu, Y.; Liu, W.; Xu, H.; Yang, L.; Liu, Y. CsPbBr_3 -Quantum-Dots/Polystyrene@Silica Hybrid Microsphere Structures with Significantly Improved Stability for White LEDs. *Adv. Opt. Mater.* **2019**, *1900546*.

(458) Huang, S.; Li, Z.; Kong, L.; Zhu, N.; Shan, A.; Li, L. Enhancing the Stability of $\text{CH}_3\text{NH}_3\text{PbBr}_3$ Quantum Dots by Embedding in Silica Spheres Derived from Tetramethyl Orthosilicate in "Waterless" Toluene. *J. Am. Chem. Soc.* **2016**, *138*, 5749–5752.

(459) Zhang, X.; Bai, X.; Wu, H.; Zhang, X.; Sun, C.; Zhang, Y.; Zhang, W.; Zheng, W.; Yu, W. W.; Rogach, A. L. Water-Assisted Size and Shape Control of CsPbBr_3 Perovskite Nanocrystals. *Angew. Chem., Int. Ed.* **2018**, *57*, 3337–3342.

(460) Shao, G.; Zhao, Y.; Yu, Y.; Yang, H.; Liu, X.; Zhang, Y.; Xiang, W.; Liang, X. Bright Emission and High Photoluminescence CsPb_2Br_5 NCs Encapsulated in Mesoporous Silica with Ultrahigh Stability and Excellent Optical Properties for White Light-Emitting Diodes. *J. Mater. Chem. C* **2019**, *7*, 13585–13593.

(461) You, X.; Wu, J.; Chi, Y. Superhydrophobic Silica Aerogels Encapsulated Fluorescent Perovskite Quantum Dots for Reversible Sensing of SO_2 in a 3D-Printed Gas Cell. *Anal. Chem.* **2019**, *91*, 5058–5066.

(462) Huang, H.; Chen, B.; Wang, Z.; Hung, T. F.; Susha, A. S.; Zhong, H.; Rogach, A. L. Water Resistant CsPbX_3 Nanocrystals Coated with Polyhedral Oligomeric Silsesquioxane and Their Use as Solid State Luminophores in All-Perovskite White Light-Emitting Devices. *Chem. Sci.* **2016**, *7*, S699–S703.

(463) Ye, Y.; Zhang, W.; Zhao, Z.; Wang, J.; Liu, C.; Deng, Z.; Zhao, X.; Han, J. Highly Luminescent Cesium Lead Halide Perovskite

Nanocrystals Stabilized in Glasses for Light-Emitting Applications. *Adv. Opt. Mater.* **2019**, *7*, 1801663.

(464) Yuan, S.; Chen, D.; Li, X.; Zhong, J.; Xu, X. *In Situ* Crystallization Synthesis of CsPbBr_3 Perovskite Quantum Dot-Embedded Glasses with Improved Stability for Solid-State Lighting and Random Upconverted Lasing. *ACS Appl. Mater. Interfaces* **2018**, *10*, 18918–18926.

(465) Di, X.; Hu, Z.; Jiang, J.; He, M.; Zhou, L.; Xiang, W.; Liang, X. Use of Long-Term Stable CsPbBr_3 Perovskite Quantum Dots in Phospho-Silicate Glass for Highly Efficient White Leds. *Chem. Commun.* **2017**, *53*, 11068–11071.

(466) An, M. N.; Park, S.; Brescia, R.; Lutfullin, M.; Sinatra, L.; Bakr, O. M.; De Trizio, L.; Manna, L. Low-Temperature Molten Salts Synthesis: CsPbBr_3 Nanocrystals with High Photoluminescence Emission Buried in Mesoporous SiO_2 . *ACS Energy Lett.* **2021**, *6*, 900–907.

(467) Chen, K.; Schunemann, S.; Tuysuz, H. Preparation of Waterproof Organometal Halide Perovskite Photonic Crystal Beads. *Angew. Chem., Int. Ed.* **2017**, *56*, 6548–6552.

(468) Shi, J.; Ge, W.; Gao, W.; Xu, M.; Zhu, J.; Li, Y. Enhanced Thermal Stability of Halide Perovskite CsPbX_3 Nanocrystals by a Facile TPU Encapsulation. *Adv. Opt. Mater.* **2020**, *8*, 1901516.

(469) Raja, S. N.; Bekenstein, Y.; Koc, M. A.; Fischer, S.; Zhang, D.; Lin, L.; Ritchie, R. O.; Yang, P.; Alivisatos, A. P. Encapsulation of Perovskite Nanocrystals into Macroscale Polymer Matrices: Enhanced Stability and Polarization. *ACS Appl. Mater. Interfaces* **2016**, *8*, 35523–35533.

(470) Li, Y.; Lv, Y.; Guo, Z.; Dong, L.; Zheng, J.; Chai, C.; Chen, N.; Lu, Y.; Chen, C. One-Step Preparation of Long-Term Stable and Flexible CsPbBr_3 Perovskite Quantum Dots/Ethylene Vinyl Acetate Copolymer Composite Films for White Light-Emitting Diodes. *ACS Appl. Mater. Interfaces* **2018**, *10*, 15888–15894.

(471) Hintermayr, V. A.; Lampe, C.; Low, M.; Roemer, J.; Vanderlinden, W.; Gramlich, M.; Bohm, A. X.; Sattler, C.; Nickel, B.; Lohmuller, T.; Urban, A. S. Polymer Nanoreactors Shield Perovskite Nanocrystals from Degradation. *Nano Lett.* **2019**, *19*, 4928–4933.

(472) Yin, B.; Sadtler, B.; Berezin, M. Y.; Thimsen, E. Quantum Dots Protected from Oxidative Attack Using Alumina Shells Synthesized by Atomic Layer Deposition. *Chem. Commun.* **2016**, *52*, 11127–11130.

(473) Liu, Y.; Gibbs, M.; Perkins, C. L.; Tolentino, J.; Zarghami, M. H.; Bustamante, J., Jr.; Law, M. Robust, Functional Nanocrystal Solids by Infilling with Atomic Layer Deposition. *Nano Lett.* **2011**, *11*, 5349–5355.

(474) Pourret, A.; Guyot-Sionnest, P.; Elam, J. W. Atomic Layer Deposition of ZnO in Quantum Dot Thin Films. *Adv. Mater.* **2009**, *21*, 232–235.

(475) Loiudice, A.; Saris, S.; Oveisi, E.; Alexander, D. T. L.; Buonsanti, R. CsPbBr_3 QD/ AlO_x Inorganic Nanocomposites with Exceptional Stability in Water, Light, and Heat. *Angew. Chem., Int. Ed.* **2017**, *56*, 10696–10701.

(476) Guo, T.; Bose, R.; Zhou, X.; Gartstein, Y. N.; Yang, H.; Kwon, S.; Kim, M. J.; Lutfullin, M.; Sinatra, L.; Gereige, I.; Al-Saggaf, A.; Bakr, O. M.; Mohammed, O. F.; Malko, A. V. Delayed Photoluminescence and Modified Blinking Statistics in Alumina-Encapsulated Zero-Dimensional Inorganic Perovskite Nanocrystals. *J. Phys. Chem. Lett.* **2019**, *10*, 6780–6787.

(477) Buonsanti, R.; Loiudice, A.; Niemann, V.; Dona, S.; Saris, S. Optimizing the Atomic Layer Deposition of Alumina on Perovskite Nanocrystal Films by Using O_2 as a Molecular Probe. *Helv. Chim. Acta* **2020**, *103*, e2000055.

(478) Zheng, Z.; Zhuge, F.; Wang, Y.; Zhang, J.; Gan, L.; Zhou, X.; Li, H.; Zhai, T. Decorating Perovskite Quantum Dots in TiO_2 Nanotubes Array for Broadband Response Photodetector. *Adv. Funct. Mater.* **2017**, *27*, 1703115.

(479) Wang, B.; Zhang, C.; Zheng, W.; Zhang, Q.; Bao, Z.; Kong, L.; Li, L. Large-Scale Synthesis of Highly Luminescent Perovskite Nanocrystals by Template-Assisted Solid-State Reaction at 800° C. *Chem. Mater.* **2020**, *32*, 308–314.

(480) Zhang, D.; Xu, Y.; Liu, Q.; Xia, Z. Encapsulation of $\text{CH}_3\text{NH}_3\text{PbBr}_3$ Perovskite Quantum Dots in MOF-5 Microcrystals as a Stable Platform for Temperature and Aqueous Heavy Metal Ion Detection. *Inorg. Chem.* **2018**, *57*, 4613–4619.

(481) Ren, J. J.; Li, T. R.; Zhou, X. P.; Dong, X.; Shorokhov, A. V.; Semenov, M. B.; Krevchik, V. D.; Wang, Y. H. Encapsulating All-Inorganic Perovskite Quantum Dots into Mesoporous Metal Organic Frameworks with Significantly Enhanced Stability for Optoelectronic Applications. *Chem. Eng. J.* **2019**, *358*, 30–39.

(482) Wu, L. Y.; Mu, Y. F.; Guo, X. X.; Zhang, W.; Zhang, Z. M.; Zhang, M.; Lu, T. B. Encapsulating Perovskite Quantum Dots in Iron-Based Metal-Organic Frameworks (MOFs) for Efficient Photocatalytic CO_2 Reduction. *Angew. Chem., Int. Ed.* **2019**, *58*, 9491–9495.

(483) Zhang, C.; Wang, B.; Li, W.; Huang, S.; Kong, L.; Li, Z.; Li, L. Conversion of Invisible Metal-Organic Frameworks to Luminescent Perovskite Nanocrystals for Confidential Information Encryption and Decryption. *Nat. Commun.* **2017**, *8*, 1138.

(484) Zhang, D.; Zhou, W.; Liu, Q.; Xia, Z. $\text{CH}_3\text{NH}_3\text{PbBr}_3$ Perovskite Nanocrystals Encapsulated in Lanthanide Metal–Organic Frameworks as a Photoluminescence Converter for Anti-Counterfeiting. *ACS Appl. Mater. Interfaces* **2018**, *10*, 27875–27884.

(485) Wei, Y.; Xiao, H.; Xie, Z.; Liang, S.; Liang, S.; Cai, X.; Huang, S.; Al Kheraif, A. A.; Jang, H. S.; Cheng, Z.; Lin, J. Highly Luminescent Lead Halide Perovskite Quantum Dots in Hierarchical CaF_2 Matrices with Enhanced Stability as Phosphors for White Light-Emitting Diodes. *Adv. Opt. Mater.* **2018**, *6*, 1701343.

(486) Yang, J.-N.; Song, Y.; Yao, J.-S.; Wang, K.-H.; Wang, J.-J.; Zhu, B.-S.; Yao, M.-M.; Rahman, S. U.; Lan, Y.-F.; Fan, F.-J.; Yao, H.-B. Potassium Bromide Surface Passivation on $\text{CsPbI}_3\text{-xBr}_x$ Nanocrystals for Efficient and Stable Pure Red Perovskite Light-Emitting Diodes. *J. Am. Chem. Soc.* **2020**, *142*, 2956–2967.

(487) Müller, M.; Kaiser, M.; Stachowski, G. M.; Resch-Genger, U.; Gaponik, N.; Eychmüller, A. Photoluminescence Quantum Yield and Matrix-Induced Luminescence Enhancement of Colloidal Quantum Dots Embedded in Ionic Crystals. *Chem. Mater.* **2014**, *26*, 3231–3237.

(488) Adam, M.; Tietze, R.; Gaponik, N.; Eychmüller, A. QD-Salt Mixed Crystals: The Influence of Salt-Type, Free-Stabilizer, and pH. *Z. Phys. Chem.* **2015**, *229*, 109–118.

(489) Benad, A.; Guhrenz, C.; Bauer, C.; Eichler, F.; Adam, M.; Ziegler, C.; Gaponik, N.; Eychmüller, A. Cold Flow as Versatile Approach for Stable and Highly Luminescent Quantum Dot-Salt Composites. *ACS Appl. Mater. Interfaces* **2016**, *8*, 21570–21575.

(490) Dirin, D. N.; Benin, B. M.; Yakunin, S.; Krumeich, F.; Raino, G.; Frison, R.; Kovalenko, M. V. Microcarrier-Assisted Inorganic Shelling of Lead Halide Perovskite Nanocrystals. *ACS Nano* **2019**, *13*, 11642–11652.

(491) Rogach, A. L. *Semiconductor Nanocrystal Quantum Dots: Synthesis, Assembly, Spectroscopy and Applications*; Springer-Verlag/Wien: New York, 2008.

(492) Chen, W.; Hao, J.; Hu, W.; Zang, Z.; Tang, X.; Fang, L.; Niu, T.; Zhou, M. Enhanced Stability and Tunable Photoluminescence in Perovskite CsPbX_3 / ZnS Quantum Dot Heterostructure. *Small* **2017**, *13*, 1604085.

(493) Akkerman, Q. A.; Abdelhady, A. L.; Manna, L. Zero-Dimensional Cesium Lead Halides: History, Properties, and Challenges. *J. Phys. Chem. Lett.* **2018**, *9*, 2326–2337.

(494) Cao, F.; Yu, D.; Ma, W.; Xu, X.; Cai, B.; Yang, Y. M.; Liu, S.; He, L.; Ke, Y.; Lan, S.; Choy, K. L.; Zeng, H. Shining Emitter in a Stable Host: Design of Halide Perovskite Scintillators for X-Ray Imaging from Commercial Concept. *ACS Nano* **2020**, *14*, 5183–5193.

(495) Hu, H.; Wu, L.; Tan, Y.; Zhong, Q.; Chen, M.; Qiu, Y.; Yang, D.; Sun, B.; Zhang, Q.; Yin, Y. Interfacial Synthesis of Highly Stable CsPbX_3 /Oxide Janus Nanoparticles. *J. Am. Chem. Soc.* **2018**, *140*, 406–412.

(496) Zhong, Q.; Cao, M.; Hu, H.; Yang, D.; Chen, M.; Li, P.; Wu, L.; Zhang, Q. One-Pot Synthesis of Highly Stable $\text{CsPbBr}_3@\text{SiO}_2$ Core–Shell Nanoparticles. *ACS Nano* **2018**, *12*, 8579–8587.

(497) Tang, X.; Chen, W.; Liu, Z.; Du, J.; Yao, Z.; Huang, Y.; Chen, C.; Yang, Z.; Shi, T.; Hu, W.; Zang, Z.; Chen, Y.; Leng, Y. Ultrathin, Core–Shell Structured SiO_2 Coated Mn^{2+} -Doped Perovskite Quantum Dots for Bright White Light-Emitting Diodes. *Small* **2019**, *15*, 1900484.

(498) Dabbousi, B. O.; Rodriguez-Viejo, J.; Mikulec, F. V.; Heine, J. R.; Mattoussi, H.; Ober, R.; Jensen, K. F.; Bawendi, M. G. (CdSe)ZnS Core–Shell Quantum Dots: Synthesis and Characterization of a Size Series of Highly Luminescent Nanocrystallites. *J. Phys. Chem. B* **1997**, *101*, 9463–9475.

(499) Luo, J.; Wang, X.; Li, S.; Liu, J.; Guo, Y.; Niu, G.; Yao, L.; Fu, Y.; Gao, L.; Dong, Q.; Zhao, C.; Leng, M.; Ma, F.; Liang, W.; Wang, L.; Jin, S.; Han, J.; Zhang, L.; Etheridge, J.; Wang, J.; Yan, Y.; Sargent, E. H.; Tang, J. Efficient and Stable Emission of Warm-White Light from Lead-Free Halide Double Perovskites. *Nature* **2018**, *563*, 541–545.

(500) Qiao, B.; Song, P.; Cao, J.; Zhao, S.; Shen, Z.; Gao, D.; Liang, Z.; Xu, Z.; Song, D.; Xu, X. Water-Resistant, Monodispersed and Stably Luminescent $\text{CsPbBr}_3/\text{CsPb}_2\text{Br}_5$ Core–Shell-Like Structure Lead Halide Perovskite Nanocrystals. *Nanotechnology* **2017**, *28*, 445602.

(501) Tang, X.; Yang, J.; Li, S.; Chen, W.; Hu, Z.; Qiu, J. $\text{CsPbBr}_3/\text{CdS}$ Core/Shell Structure Quantum Dots for Inverted Light-Emitting Diodes Application. *Front. Chem.* **2019**, *7*, 499.

(502) Eorpach, A. t. Official Journal of the European Union. 2017, L 281.

(503) Sun, J.; Yang, J.; Lee, J. I.; Cho, J. H.; Kang, M. S. Lead-Free Perovskite Nanocrystals for Light-Emitting Devices. *J. Phys. Chem. Lett.* **2018**, *9*, 1573–1583.

(504) Khalfin, S.; Bekenstein, Y. Advances in Lead-Free Double Perovskite Nanocrystals, Engineering Band-Gaps and Enhancing Stability through Composition Tunability. *Nanoscale* **2019**, *11*, 8665–8679.

(505) Fan, Q.; Biesold-McGee, G. V.; Ma, J.; Xu, Q.; Pan, S.; Peng, J.; Lin, Z. Lead-Free Halide Perovskite Nanocrystals: Crystal Structures, Synthesis, Stabilities, and Optical Properties. *Angew. Chem., Int. Ed.* **2020**, *59*, 1030–1046.

(506) Zhu, D.; Zito, J.; Pinchetti, V.; Dang, Z.; Olivati, A.; Pasquale, L.; Tang, A.; Zaffalon, M. L.; Meinardi, F.; Infante, I.; De Trizio, L.; Manna, L.; Brovelli, S. Compositional Tuning of Carrier Dynamics in $\text{Cs}_2\text{Na}_{1-x}\text{Ag}_x\text{BiCl}_6$ Double-Perovskite Nanocrystals. *ACS Energy Lett.* **2020**, *5*, 1840–1847.

(507) Xia, Z.; Liu, Y.; Nag, A.; Manna, L. Lead-Free Double Perovskite $\text{Cs}_2\text{AgInCl}_6$. *Angew. Chem., Int. Ed.* **2021**, DOI: [10.1002/anie.202011833](https://doi.org/10.1002/anie.202011833).

(508) Zhang, B.; Wang, M.; Ghini, M.; Melcherts, A. E. M.; Zito, J.; Goldoni, L.; Infante, I.; Guizzardi, M.; Scotognella, F.; Kriegel, I.; De Trizio, L.; Manna, L. Colloidal Bi-Doped $\text{Cs}_2\text{Ag}_{1-x}\text{Na}_x\text{InCl}_6$ Nanocrystals: Undercoordinated Surface Cl Ions Limit Their Light Emission Efficiency. *ACS Mater. Lett.* **2020**, *2*, 1442–1449.

(509) Zhu, P.; Chen, C.; Gu, S.; Lin, R.; Zhu, J. CsSnI_3 Solar Cells via an Evaporation-Assisted Solution Method. *Solar RRL* **2018**, *2*, 1700224.

(510) Chen, M.; Ju, M.-G.; Garces, H. F.; Carl, A. D.; Ono, L. K.; Hawash, Z.; Zhang, Y.; Shen, T.; Qi, Y.; Grimm, R. L.; Pacifici, D.; Zeng, X. C.; Zhou, Y.; Padture, N. P. Highly Stable and Efficient All-Inorganic Lead-Free Perovskite Solar Cells with Native-Oxide Passivation. *Nat. Commun.* **2019**, *10*, 16.

(511) Sabba, D.; Malmudi, H. K.; Prabhakar, R. R.; Krishnamoorthy, T.; Baikie, T.; Boix, P. P.; Mhaisalkar, S.; Mathews, N. Impact of Anionic Br– Substitution on Open Circuit Voltage in Lead Free Perovskite ($\text{CsSnI}_{3-x}\text{Br}_x$) Solar Cells. *J. Phys. Chem. C* **2015**, *119*, 1763–1767.

(512) Ke, W.; Stoumpos, C. C.; Zhu, M.; Mao, L.; Spanopoulos, I.; Liu, J.; Kontsevoi, O. Y.; Chen, M.; Sarma, D.; Zhang, Y.; Wasielewski, M. R.; Kanatzidis, M. G. Enhanced Photovoltaic Performance and Stability with a New Type of Hollow 3D Perovskite $\{\text{en}\}\text{FASnI}_3$. *Sci. Adv.* **2017**, *3*, e1701293.

(513) Krishnamoorthy, T.; Ding, H.; Yan, C.; Leong, W. L.; Baikie, T.; Zhang, Z.; Sherburne, M.; Li, S.; Asta, M.; Mathews, N.; Mhaisalkar, S. G. Lead-Free Germanium Iodide Perovskite Materials for Photovoltaic Applications. *J. Mater. Chem. A* **2015**, *3*, 23829–23832.

(514) Ju, M.-G.; Dai, J.; Ma, L.; Zeng, X. C. Lead-Free Mixed Tin and Germanium Perovskites for Photovoltaic Application. *J. Am. Chem. Soc.* **2017**, *139*, 8038–8043.

(515) Jellicoe, T. C.; Richter, J. M.; Glass, H. F. J.; Tabachnyk, M.; Brady, R.; Dutton, S. E.; Rao, A.; Friend, R. H.; Credgington, D.; Greenham, N. C.; Böhm, M. L. Synthesis and Optical Properties of Lead-Free Cesium Tin Halide Perovskite Nanocrystals. *J. Am. Chem. Soc.* **2016**, *138*, 2941–2944.

(516) Wong, A. B.; Bekenstein, Y.; Kang, J.; Kley, C. S.; Kim, D.; Gibson, N. A.; Zhang, D.; Yu, Y.; Leone, S. R.; Wang, L.-W.; Alivisatos, A. P.; Yang, P. Strongly Quantum Confined Colloidal Cesium Tin Iodide Perovskite Nanoplates: Lessons for Reducing Defect Density and Improving Stability. *Nano Lett.* **2018**, *18*, 2060–2066.

(517) Chen, L.-J.; Lee, C.-R.; Chuang, Y.-J.; Wu, Z.-H.; Chen, C. Synthesis and Optical Properties of Lead-Free Cesium Tin Halide Perovskite Quantum Rods with High-Performance Solar Cell Application. *J. Phys. Chem. Lett.* **2016**, *7*, 5028–5035.

(518) Hao, F.; Stoumpos, C. C.; Cao, D. H.; Chang, R. P. H.; Kanatzidis, M. G. Lead-Free Solid-State Organic–Inorganic Halide Perovskite Solar Cells. *Nat. Photonics* **2014**, *8*, 489–494.

(519) Huang, L.-y.; Lambrecht, W. R. L. Electronic Band Structure, Phonons, and Exciton Binding Energies of Halide Perovskites CsSnCl_3 , CsSnBr_3 and CsSnI_3 . *Phys. Rev. B: Condens. Matter Mater. Phys.* **2013**, *88*, 165203.

(520) Yan, J.; Qiu, W.; Wu, G.; Heremans, P.; Chen, H. Recent Progress in 2D/Quasi-2D Layered Metal Halide Perovskites for Solar Cells. *J. Mater. Chem. A* **2018**, *6*, 11063–11077.

(521) Chung, I.; Song, J.-H.; Im, J.; Androulakis, J.; Malliakas, C. D.; Li, H.; Freeman, A. J.; Kenney, J. T.; Kanatzidis, M. G. CsSnI_3 : Semiconductor or Metal? High Electrical Conductivity and Strong Near-Infrared Photoluminescence from a Single Material. High Hole Mobility and Phase-Transitions. *J. Am. Chem. Soc.* **2012**, *134*, 8579–8587.

(522) Wang, A.; Yan, X.; Zhang, M.; Sun, S.; Yang, M.; Shen, W.; Pan, X.; Wang, P.; Deng, Z. Controlled Synthesis of Lead-Free and Stable Perovskite Derivative Cs_2SnI_6 Nanocrystals via a Facile Hot-Injection Process. *Chem. Mater.* **2016**, *28*, 8132–8140.

(523) Huang, J.; Lei, T.; Siron, M.; Zhang, Y.; Yu, S.; Seeler, F.; Dehestani, A.; Quan, L. N.; Schierle-Arndt, K.; Yang, P. Lead-free Cesium Europium Halide Perovskite Nanocrystals. *Nano Lett.* **2020**, *20*, 3734–3739.

(524) Chiara, R.; Ciftci, Y. O.; Queloz, V. I. E.; Nazeeruddin, M. K.; Grancini, G.; Malavasi, L. Green-Emitting Lead-Free Cs_2SnBr_6 Zero-Dimensional Perovskite Nanocrystals with Improved Air Stability. *J. Phys. Chem. Lett.* **2020**, *11*, 618–623.

(525) Xing, G.; Kumar, M. H.; Chong, W. K.; Liu, X.; Cai, Y.; Ding, H.; Asta, M.; Grätzel, M.; Mhaisalkar, S.; Mathews, N.; Sum, T. C. Solution-Processed Tin-Based Perovskite for Near-Infrared Lasing. *Adv. Mater.* **2016**, *28*, 8191–8196.

(526) Wang, A.; Guo, Y.; Muhammad, F.; Deng, Z. Controlled Synthesis of Lead-Free Cesium Tin Halide Perovskite Cubic Nanocages with High Stability. *Chem. Mater.* **2017**, *29*, 6493–6501.

(527) Wang, C.; Zhang, Y.; Wang, A.; Wang, Q.; Tang, H.; Shen, W.; Li, Z.; Deng, Z. Controlled Synthesis of Composition Tunable Formamidinium Cesium Double Cation Lead Halide Perovskite Nanowires and Nanosheets with Improved Stability. *Chem. Mater.* **2017**, *29*, 2157–2166.

(528) Liu, F.; Zhang, Y.; Ding, C.; Kawabata, K.; Yoshihara, Y.; Toyoda, T.; Hayase, S.; Minemoto, T.; Wang, R.; Shen, Q. Trioctylphosphine Oxide Acts as Alkahest for $\text{SnX}_2/\text{PbX}_2$: A General

Synthetic Route to Perovskite $ASn_xPb_{1-x}X_3$ ($A = Cs, FA, MA$; $X = Cl, Br, I$) Quantum Dots. *Chem. Mater.* **2020**, *32*, 1089–1100.

(529) Vitoreti, A. B. F.; Agouram, S.; Solis de la Fuente, M.; Muñoz-Sanjosé, V.; Schiavon, M. A.; Mora-Seró, I. Study of the Partial Substitution of Pb by Sn in Cs–Pb–Sn–Br Nanocrystals Owing to Obtaining Stable Nanoparticles with Excellent Optical Properties. *J. Phys. Chem. C* **2018**, *122*, 14222–14231.

(530) Liu, F.; Ding, C.; Zhang, Y.; Ripolles, T. S.; Kamisaka, T.; Toyoda, T.; Hayase, S.; Minemoto, T.; Yoshino, K.; Dai, S.; Yanagida, M.; Noguchi, H.; Shen, Q. Colloidal Synthesis of Air-Stable Alloyed $CsSn_{1-x}Pb_xI_3$ Perovskite Nanocrystals for Use in Solar Cells. *J. Am. Chem. Soc.* **2017**, *139*, 16708–16719.

(531) Deng, J.; Wang, H.; Xun, J.; Wang, J.; Yang, X.; Shen, W.; Li, M.; He, R. Room-Temperature Synthesis of Excellent-Performance $CsPb_{1-x}Sn_xBr_3$ Perovskite Quantum Dots and Application in Light-Emitting Diodes. *Mater. Des.* **2020**, *185*, 108246.

(532) Palmstrom, A. F.; Eperon, G. E.; Leijtens, T.; Prasanna, R.; Haberreuter, S. N.; Nemeth, W.; Gaulding, E. A.; Dunfield, S. P.; Reese, M.; Nanayakkara, S.; Moot, T.; Werner, J.; Liu, J.; To, B.; Christensen, S. T.; McGehee, M. D.; van Hest, M. F. A. M.; Luther, J. M.; Berry, J. J.; Moore, D. T. Enabling Flexible All-Perovskite Tandem Solar Cells. *Joule* **2019**, *3*, 2193–2204.

(533) Selvarajan, P.; Kundu, K.; Sathish, C. I.; Umapathy, S.; Vinu, A. Enriched Photophysical Properties and Thermal Stability of Tin(II) Substituted Lead-Based Perovskite Nanocrystals with Mixed Organic–Inorganic Cations. *J. Phys. Chem. C* **2020**, *124*, 9611–9621.

(534) Dolzhnikov, D. S.; Wang, C.; Xu, Y.; Kanatzidis, M. G.; Weiss, E. A. Ligand-Free, Quantum-Confining Cs_2SnI_6 Perovskite Nanocrystals. *Chem. Mater.* **2017**, *29*, 7901–7907.

(535) Ghosh, S.; Paul, S.; De, S. K. Control Synthesis of Air-Stable Morphology Tunable Pb-Free Cs_2SnI_6 Perovskite Nanoparticles and Their Photodetection Properties. *Part. Part. Syst. Char.* **2018**, *35*, 1800199.

(536) Leng, M.; Yang, Y.; Chen, Z.; Gao, W.; Zhang, J.; Niu, G.; Li, D.; Song, H.; Zhang, J.; Jin, S.; Tang, J. Surface Passivation of Bismuth-Based Perovskite Variant Quantum Dots To Achieve Efficient Blue Emission. *Nano Lett.* **2018**, *18*, 6076–6083.

(537) Men, L.; Rosales, B. A.; Gentry, N. E.; Cady, S. D.; Vela, J. Lead-Free Semiconductors: Soft Chemistry, Dimensionality Control, and Manganese-Doping of Germanium Halide Perovskites. *Chem-NanoMat* **2019**, *5*, 334–339.

(538) Chen, L.-J. Synthesis and Optical Properties of Lead-Free Cesium Germanium Halide Perovskite Quantum Rods. *RSC Adv.* **2018**, *8*, 18396–18399.

(539) Moon, B. J.; Kim, S. J.; Lee, S.; Lee, A.; Lee, H.; Lee, D. S.; Kim, T.-W.; Lee, S.-K.; Bae, S.; Lee, S. H. Rare-Earth-Element-Ytterbium-Substituted Lead-Free Inorganic Perovskite Nanocrystals for Optoelectronic Applications. *Adv. Mater.* **2019**, *31*, 1901716.

(540) He, T.; Li, J.; Li, X.; Ren, C.; Luo, Y.; Zhao, F.; Chen, R.; Lin, X.; Zhang, J. Spectroscopic Studies of Chiral Perovskite Nanocrystals. *Appl. Phys. Lett.* **2017**, *111*, 151102.

(541) McCall, K. M.; Stoumpos, C. C.; Kostina, S. S.; Kanatzidis, M. G.; Wessels, B. W. Strong Electron–Phonon Coupling and Self-Trapped Excitons in the Defect Halide Perovskites $A_3M_2I_9$ ($A = Cs, Rb; M = Bi, Sb$). *Chem. Mater.* **2017**, *29*, 4129–4145.

(542) Zuo, C.; Ding, L. Lead-Free Perovskite Materials $(NH_4)_3Sb_2I_xBr_{9-x}$. *Angew. Chem., Int. Ed.* **2017**, *56*, 6528–6532.

(543) Yang, B.; Chen, J.; Hong, F.; Mao, X.; Zheng, K.; Yang, S.; Li, Y.; Pullerits, T.; Deng, W.; Han, K. Lead-Free, Air-Stable All-Inorganic Cesium Bismuth Halide Perovskite Nanocrystals. *Angew. Chem., Int. Ed.* **2017**, *56*, 12471–12475.

(544) Pal, J.; Manna, S.; Mondal, A.; Das, S.; Adarsh, K. V.; Nag, A. Colloidal Synthesis and Photophysics of $M_3Sb_2I_9$ ($M = Cs$ and Rb) Nanocrystals: Lead-Free Perovskites. *Angew. Chem., Int. Ed.* **2017**, *56*, 14187–14191.

(545) Pal, J.; Bhunia, A.; Chakraborty, S.; Manna, S.; Das, S.; Dewan, A.; Datta, S.; Nag, A. Synthesis and Optical Properties of Colloidal $M_3Bi_2I_9$ ($M = Cs, Rb$) Perovskite Nanocrystals. *J. Phys. Chem. C* **2018**, *122*, 10643–10649.

(546) Cai, T.; Shi, W.; Hwang, S.; Kobbekaduwa, K.; Nagaoka, Y.; Yang, H.; Hills-Kimball, K.; Zhu, H.; Wang, J.; Wang, Z.; Liu, Y.; Su, D.; Gao, J.; Chen, O. Lead-Free $Cs_4CuSb_2Cl_{12}$ Layered Double Perovskite Nanocrystals. *J. Am. Chem. Soc.* **2020**, *142*, 11927–11936.

(547) Ma, Z.; Shi, Z.; Yang, D.; Zhang, F.; Li, S.; Wang, L.; Wu, D.; Zhang, Y.; Na, G.; Zhang, L.; Li, X.; Zhang, Y.; Shan, C. Electrically-Driven Violet Light-Emitting Devices Based on Highly Stable Lead-Free Perovskite $Cs_3Sb_2Br_9$ Quantum Dots. *ACS Energy Lett.* **2020**, *5*, 385–394.

(548) Johnston, A.; Dinic, F.; Todorović, P.; Chen, B.; Sagar, L. K.; Saidaminov, M. I.; Hoogland, S.; Voznyy, O.; Sargent, E. H. Narrow Emission from $Rb_3Sb_2I_9$ Nanoparticles. *Adv. Opt. Mater.* **2020**, *8*, 1901606.

(549) Pradhan, B.; Kumar, G. S.; Sain, S.; Dalui, A.; Ghorai, U. K.; Pradhan, S. K.; Acharya, S. Size Tunable Cesium Antimony Chloride Perovskite Nanowires and Nanorods. *Chem. Mater.* **2018**, *30*, 2135–2142.

(550) Zhang, J.; Yang, Y.; Deng, H.; Farooq, U.; Yang, X.; Khan, J.; Tang, J.; Song, H. High Quantum Yield Blue Emission from Lead-Free Inorganic Antimony Halide Perovskite Colloidal Quantum Dots. *ACS Nano* **2017**, *11*, 9294–9302.

(551) Leng, M.; Yang, Y.; Zeng, K.; Chen, Z.; Tan, Z.; Li, S.; Li, J.; Xu, B.; Li, D.; Hautzinger, M. P.; Fu, Y.; Zhai, T.; Xu, L.; Niu, G.; Jin, S.; Tang, J. All-Inorganic Bismuth-Based Perovskite Quantum Dots with Bright Blue Photoluminescence and Excellent Stability. *Adv. Funct. Mater.* **2018**, *28*, 1704446.

(552) Paternò, G. M.; Mishra, N.; Barker, A. J.; Dang, Z.; Lanzani, G.; Manna, L.; Petrozza, A. Broadband Defects Emission and Enhanced Ligand Raman Scattering in 0D $Cs_3Bi_2I_9$ Colloidal Nanocrystals. *Adv. Funct. Mater.* **2019**, *29*, 1805299.

(553) Lou, Y.; Fang, M.; Chen, J.; Zhao, Y. Formation of Highly Luminescent Cesium Bismuth Halide Perovskite Quantum Dots Tuned by Anion Exchange. *Chem. Commun.* **2018**, *54*, 3779–3782.

(554) Mir, W. J.; Warankar, A.; Acharya, A.; Das, S.; Mandal, P.; Nag, A. Colloidal Thallium Halide Nanocrystals with Reasonable Luminescence, Carrier Mobility and Diffusion Length. *Chem. Sci.* **2017**, *8*, 4602–4611.

(555) Galván-Arzate, S.; Santamaría, A. Thallium Toxicity. *Toxicol. Lett.* **1998**, *99*, 1–13.

(556) Zhou, L.; Xu, Y.-F.; Chen, B.-X.; Kuang, D.-B.; Su, C.-Y. Synthesis and Photocatalytic Application of Stable Lead-Free $Cs_2AgBiBr_6$ Perovskite Nanocrystals. *Small* **2018**, *14*, 1703762.

(557) Booker, E. P.; Griffiths, J. T.; Eyre, L.; Ducati, C.; Greenham, N. C.; Davis, N. J. L. K. Synthesis, Characterization, and Morphological Control of Cs_2CuCl_4 Nanocrystals. *J. Phys. Chem. C* **2019**, *123*, 16951–16956.

(558) Li, Y.; Vashishtha, P.; Zhou, Z.; Li, Z.; Shivarudraiah, S. B.; Ma, C.; Liu, J.; Wong, K. S.; Su, H.; Halpert, J. E. Room Temperature Synthesis of Stable, Printable $Cs_3Cu_2X_5$ ($X = I, Br/I, Br, Br/Cl, Cl$) Colloidal Nanocrystals with Near-Unity Quantum Yield Green Emitters ($X = Cl$). *Chem. Mater.* **2020**, *32*, 5515–5524.

(559) Luo, Z.; Li, Q.; Zhang, L.; Wu, X.; Tan, L.; Zou, C.; Liu, Y.; Quan, Z. 0D $Cs_3Cu_2X_5$ ($X = I, Br$, and Cl) Nanocrystals: Colloidal Syntheses and Optical Properties. *Small* **2020**, *16*, 1905226.

(560) Dahl, J. C.; Osowiecki, W. T.; Cai, Y.; Swabeck, J. K.; Bekenstein, Y.; Asta, M.; Chan, E. M.; Alivisatos, A. P. Probing the Stability and Band Gaps of $Cs_2AgInCl_6$ and $Cs_2AgSbCl_6$ Lead-Free Double Perovskite Nanocrystals. *Chem. Mater.* **2019**, *31*, 3134–3143.

(561) Han, P.; Zhang, X.; Luo, C.; Zhou, W.; Yang, S.; Zhao, J.; Deng, W.; Han, K. Manganese-Doped, Lead-Free Double Perovskite Nanocrystals for Bright Orange-Red Emission. *ACS Cent. Sci.* **2020**, *6*, 566–572.

(562) Chen, N.; Cai, T.; Li, W.; Hills-Kimball, K.; Yang, H.; Que, M.; Nagaoka, Y.; Liu, Z.; Yang, D.; Dong, A.; Xu, C.-Y.; Zia, R.; Chen, O. Yb- and Mn-Doped Lead-Free Double Perovskite Cs_2AgBiX_6 ($X = Cl^-$, Br^-) Nanocrystals. *ACS Appl. Mater. Interfaces* **2019**, *11*, 16855–16863.

(563) Kshirsagar, A. S.; Nag, A. Synthesis and Optical Properties of Colloidal $Cs_2AgSb_{1-x}Bi_xCl_6$ Double Perovskite Nanocrystals. *J. Chem. Phys.* **2019**, *151*, 161101.

(564) Lamba, R. S.; Basera, P.; Bhattacharya, S.; Sapra, S. Band Gap Engineering in $Cs_2(Na_xAg_{1-x})BiCl_6$ Double Perovskite Nanocrystals. *J. Phys. Chem. Lett.* **2019**, *10*, 5173–5181.

(565) Lee, W.; Hong, S.; Kim, S. Colloidal Synthesis of Lead-Free Silver–Indium Double-Perovskite $Cs_2AgInCl_6$ Nanocrystals and Their Doping with Lanthanide Ions. *J. Phys. Chem. C* **2019**, *123*, 2665–2672.

(566) Locardi, F.; Cirignano, M.; Baranov, D.; Dang, Z.; Prato, M.; Drago, F.; Ferretti, M.; Pinchetti, V.; Fanciulli, M.; Brovelli, S.; De Trizio, L.; Manna, L. Colloidal Synthesis of Double Perovskite $Cs_2AgInCl_6$ and Mn-Doped $Cs_2AgInCl_6$ Nanocrystals. *J. Am. Chem. Soc.* **2018**, *140*, 12989–12995.

(567) Locardi, F.; Sartori, E.; Buha, J.; Zito, J.; Prato, M.; Pinchetti, V.; Zaffalon, M. L.; Ferretti, M.; Brovelli, S.; Infante, I.; De Trizio, L.; Manna, L. Emissive Bi-Doped Double Perovskite $Cs_2Ag_{1-x}Na_xInCl_6$ Nanocrystals. *ACS Energy Lett.* **2019**, *4*, 1976–1982.

(568) Mahor, Y.; Mir, W. J.; Nag, A. Synthesis and Near-Infrared Emission of Yb-Doped $Cs_2AgInCl_6$ Double Perovskite Microcrystals and Nanocrystals. *J. Phys. Chem. C* **2019**, *123*, 15787–15793.

(569) Lee, W.; Choi, D.; Kim, S. Colloidal Synthesis of Shape-Controlled Cs_2NaBiX_6 ($X = Cl, Br$) Double Perovskite Nanocrystals: Discrete Optical Transition by Non-Bonding Characters and Energy Transfer to Mn Dopants. *Chem. Mater.* **2020**, *32*, 6864–6874.

(570) Yang, Z.; Jiang, Z.; Liu, X.; Zhou, X.; Zhang, J.; Li, W. Bright Blue Light-Emitting Doped Cesium Bromide Nanocrystals: Alternatives of Lead-Free Perovskite Nanocrystals for White LEDs. *Adv. Opt. Mater.* **2019**, *7*, 1900108.

(571) Yang, B.; Hong, F.; Chen, J.; Tang, Y.; Yang, L.; Sang, Y.; Xia, X.; Guo, J.; He, H.; Yang, S.; Deng, W.; Han, K. Colloidal Synthesis and Charge-Carrier Dynamics of $Cs_2AgSb_{1-y}Bi_yX_6$ ($X: Br, Cl; 0 \leq y \leq 1$) Double Perovskite Nanocrystals. *Angew. Chem., Int. Ed.* **2019**, *58*, 2278–2283.

(572) Savory, C. N.; Walsh, A.; Scanlon, D. O. Can Pb-Free Halide Double Perovskites Support High-Efficiency Solar Cells? *ACS Energy Lett.* **2016**, *1*, 949–955.

(573) Zhou, Y.; Chen, J.; Bakr, O. M.; Sun, H.-T. Metal-Doped Lead Halide Perovskites: Synthesis, Properties, and Optoelectronic Applications. *Chem. Mater.* **2018**, *30*, 6589–6613.

(574) Liu, Y.; Jing, Y.; Zhao, J.; Liu, Q.; Xia, Z. Design Optimization of Lead-Free Perovskite $Cs_2AgInCl_6:Bi$ Nanocrystals with 11.4% Photoluminescence Quantum Yield. *Chem. Mater.* **2019**, *31*, 3333–3339.

(575) Swarnkar, A.; Chulliyil, R.; Ravi, V. K.; Irfanullah, M.; Chowdhury, A.; Nag, A. Colloidal $CsPbBr_3$ Perovskite Nanocrystals: Luminescence beyond Traditional Quantum Dots. *Angew. Chem., Int. Ed.* **2015**, *54*, 15424–15428.

(576) Han, P.; Mao, X.; Yang, S.; Zhang, F.; Yang, B.; Wei, D.; Deng, W.; Han, K. Lead-Free Sodium–Indium Double Perovskite Nanocrystals through Doping Silver Cations for Bright Yellow Emission. *Angew. Chem., Int. Ed.* **2019**, *58*, 17231–17235.

(577) Yang, B.; Mao, X.; Hong, F.; Meng, W.; Tang, Y.; Xia, X.; Yang, S.; Deng, W.; Han, K. Lead-Free Direct Band Gap Double-Perovskite Nanocrystals with Bright Dual-Color Emission. *J. Am. Chem. Soc.* **2018**, *140*, 17001–17006.

(578) K, N. N.; Nag, A. Synthesis and Luminescence of Mn-Doped $Cs_2AgInCl_6$ Double Perovskites. *Chem. Commun.* **2018**, *54*, 5205–5208.

(579) Arfin, H.; Kaur, J.; Sheikh, T.; Chakraborty, S.; Nag, A. Bi^{3+} – Er^{3+} and Bi^{3+} – Yb^{3+} Codoped $Cs_2AgInCl_6$ Double Perovskite near Infrared Emitters. *Angew. Chem., Int. Ed.* **2020**, *59*, 11307–11311.

(580) Mir, W. J.; Sheikh, T.; Arfin, H.; Xia, Z.; Nag, A. Lanthanide Doping in Metal Halide Perovskite Nanocrystals: Spectral Shifting, Quantum Cutting and Optoelectronic Applications. *NPG Asia Mater.* **2020**, *12*, 9.

(581) Tan, Z.; Li, J.; Zhang, C.; Li, Z.; Hu, Q.; Xiao, Z.; Kamiya, T.; Hosono, H.; Niu, G.; Lifshitz, E.; Cheng, Y.; Tang, J. Highly Efficient Blue-Emitting Bi-Doped Cs_2SnCl_6 Perovskite Variant: Photoluminescence Induced by Impurity Doping. *Adv. Funct. Mater.* **2018**, *28*, 1801131.

(582) Chen, L.-J.; Dai, J.-H.; Lin, J.-D.; Mo, T.-S.; Lin, H.-P.; Yeh, H.-C.; Chuang, Y.-C.; Jiang, S.-A.; Lee, C.-R. Wavelength-Tunable and Highly Stable Perovskite–Quantum-Dot-Doped Lasers with Liquid Crystal Lasing Cavities. *ACS Appl. Mater. Interfaces* **2018**, *10*, 33307–33315.

(583) Wu, H.; Yang, Y.; Zhou, D.; Li, K.; Yu, J.; Han, J.; Li, Z.; Long, Z.; Ma, J.; Qiu, J. Rb^+ Cations Enable the Change of Luminescence Properties in Perovskite ($Rb_xCs_{1-x}PbBr_3$) Quantum Dots. *Nanoscale* **2018**, *10*, 3429–3437.

(584) Zhao, X.-G.; Yang, D.; Ren, J.-C.; Sun, Y.; Xiao, Z.; Zhang, L. Rational Design of Halide Double Perovskites for Optoelectronic Applications. *Joule* **2018**, *2*, 1662–1673.

(585) Nagane, S.; Ghosh, D.; Hoye, R. L. Z.; Zhao, B.; Ahmad, S.; Walker, A. B.; Islam, M. S.; Ogale, S.; Sadhanala, A. Lead-Free Perovskite Semiconductors Based on Germanium–Tin Solid Solutions: Structural and Optoelectronic Properties. *J. Phys. Chem. C* **2018**, *122*, 5940–5947.

(586) Zhao, X.-G.; Yang, D.; Sun, Y.; Li, T.; Zhang, L.; Yu, L.; Zunger, A. Cu–In Halide Perovskite Solar Absorbers. *J. Am. Chem. Soc.* **2017**, *139*, 6718–6725.

(587) Sun, Q.; Yin, W.-J. Thermodynamic Stability Trend of Cubic Perovskites. *J. Am. Chem. Soc.* **2017**, *139*, 14905–14908.

(588) Jiang, J.; Onwudinanti, C. K.; Hatton, R. A.; Bobbert, P. A.; Tao, S. Stabilizing Lead-Free All-Inorganic Tin Halide Perovskites by Ion Exchange. *J. Phys. Chem. C* **2018**, *122*, 17660–17667.

(589) Bartel, C. J.; Clary, J. M.; Sutton, C.; Vigil-Fowler, D.; Goldsmith, B. R.; Holder, A. M.; Musgrave, C. B. Inorganic Halide Double Perovskites with Optoelectronic Properties Modulated by Sublattice Mixing. *J. Am. Chem. Soc.* **2020**, *142*, 5135–5145.

(590) Zhao, X.-G.; Yang, J.-H.; Fu, Y.; Yang, D.; Xu, Q.; Yu, L.; Wei, S.-H.; Zhang, L. Design of Lead-Free Inorganic Halide Perovskites for Solar Cells via Cation-Transmutation. *J. Am. Chem. Soc.* **2017**, *139*, 2630–2638.

(591) Li, C.; Lu, X.; Ding, W.; Feng, L.; Gao, Y.; Guo, Z. Formability of ABX_3 ($X = F, Cl, Br, I$) Halide Perovskites. *Acta Crystallogr., Sect. B: Struct. Sci.* **2008**, *64*, 702–707.

(592) Swarnkar, A.; Mir, W. J.; Chakraborty, R.; Jagadeeswararao, M.; Sheikh, T.; Nag, A. Are Chalcogenide Perovskites an Emerging Class of Semiconductors for Optoelectronic Properties and Solar Cell? *Chem. Mater.* **2019**, *31* (3), 565–575.

(593) Liu, W.; Lin, Q.; Li, H.; Wu, K.; Robel, I.; Pietryga, J. M.; Klimov, V. I. Mn^{2+} -Doped Lead Halide Perovskite Nanocrystals with Dual-Color Emission Controlled by Halide Content. *J. Am. Chem. Soc.* **2016**, *138*, 14954–14961.

(594) Sun, Q.; Wang, J.; Yin, W.-J.; Yan, Y. Bandgap Engineering of Stable Lead-Free Oxide Double Perovskites for Photovoltaics. *Adv. Mater.* **2018**, *30*, 1705901.

(595) Holzapfel, N. P.; Majher, J. D.; Strom, T. A.; Moore, C. E.; Woodward, P. M. $Cs_4Cd_{1-x}Mn_xBi_2Cl_{12}$ —A Vacancy-Ordered Halide Perovskite Phosphor with High-Efficiency Orange-Red Emission. *Chem. Mater.* **2020**, *32*, 3510–3516.

(596) Wang, L.; Shi, Z.; Ma, Z.; Yang, D.; Zhang, F.; Ji, X.; Wang, M.; Chen, X.; Na, G.; Chen, S.; Wu, D.; Zhang, Y.; Li, X.; Zhang, L.; Shan, C. Colloidal Synthesis of Ternary Copper Halide Nanocrystals for High-Efficiency Deep-Blue Light-Emitting Diodes with a Half-Lifetime above 100 h. *Nano Lett.* **2020**, *20*, 3568–3576.

(597) Qiu, W.; Xiao, Z.; Roh, K.; Noel, N. K.; Shapiro, A.; Heremans, P.; Rand, B. P. Mixed Lead–Tin Halide Perovskites for Efficient and Wavelength-Tunable Near-Infrared Light-Emitting Diodes. *Adv. Mater.* **2019**, *31*, 1806105.

(598) Zhang, X.; Wang, C.; Zhang, Y.; Zhang, X.; Wang, S.; Lu, M.; Cui, H.; Kershaw, S. V.; Yu, W. W.; Rogach, A. L. Bright Orange Electroluminescence from Lead-Free Two-Dimensional Perovskites. *ACS Energy Lett.* **2019**, *4*, 242–248.

(599) Creason, T. D.; Yangui, A.; Rocanova, R.; Strom, A.; Du, M.-H.; Saparov, B. Rb_2CuX_3 ($X = Cl, Br$): 1D All-Inorganic Copper

Halides with Ultrabright Blue Emission and Up-Conversion Photoluminescence. *Adv. Opt. Mater.* **2020**, *8*, 1901338.

(600) Yamada, T.; Aharen, T.; Kanemitsu, Y. Up-Converted Photoluminescence from $\text{CH}_3\text{NH}_3\text{PbI}_3$ Perovskite Semiconductors: Implications for Laser Cooling. *Phys. Rev. Mater.* **2019**, *3*, 024601.

(601) Mir, W. J.; Swarnkar, A.; Nag, A. Postsynthesis Mn-doping in CsPbI_3 Nanocrystals to Stabilize the Black Perovskite Phase. *Nanoscale* **2019**, *11*, 4278–4286.

(602) Paul, S.; Bladt, E.; Richter, A. F.; Döblinger, M.; Tong, Y.; Huang, H.; Dey, A.; Bals, S.; Debnath, T.; Polavarapu, L.; Feldmann, J. Manganese-Doping-Induced Quantum Confinement within Host Perovskite Nanocrystals through Ruddlesden–Popper Defects. *Angew. Chem., Int. Ed.* **2020**, *59*, 6794–6799.

(603) Pradhan, N. Mn-Doped Semiconductor Nanocrystals: 25 Years and Beyond. *J. Phys. Chem. Lett.* **2019**, *10*, 2574–2577.

(604) Parobek, D.; Roman, B. J.; Dong, Y.; Jin, H.; Lee, E.; Sheldon, M.; Son, D. H. Exciton-to-Dopant Energy Transfer in Mn-Doped Cesium Lead Halide Perovskite Nanocrystals. *Nano Lett.* **2016**, *16*, 7376–7380.

(605) Liu, W.; Lin, Q.; Li, H.; Wu, K.; Robel, I.; Pietryga, J. M.; Klimov, V. I. Mn²⁺-Doped Lead Halide Perovskite Nanocrystals with Dual-Color Emission Controlled by Halide Content. *J. Am. Chem. Soc.* **2016**, *138*, 14954–14961.

(606) Liu, H.; Wu, Z.; Shao, J.; Yao, D.; Gao, H.; Liu, Y.; Yu, W.; Zhang, H.; Yang, B. $\text{CsPb}_x\text{Mn}_{1-x}\text{Cl}_3$ Perovskite Quantum Dots with High Mn Substitution Ratio. *ACS Nano* **2017**, *11*, 2239–2247.

(607) Akkerman, Q. A.; Meggiolaro, D.; Dang, Z.; De Angelis, F.; Manna, L. Fluorescent Alloy $\text{CsPb}_x\text{Mn}_{1-x}\text{I}_3$ Perovskite Nanocrystals with High Structural and Optical Stability. *ACS Energy Lett.* **2017**, *2*, 2183–2186.

(608) Das Adhikari, S.; Dutta, S. K.; Dutta, A.; Guria, A. K.; Pradhan, N. Chemically Tailoring the Dopant Emission in Mn doped CsPbCl_3 Perovskite Nanocrystals. *Angew. Chem., Int. Ed.* **2017**, *56*, 8746–8750.

(609) Xu, K.; Lin, C. C.; Xie, X.; Meijerink, A. Efficient and Stable Luminescence from Mn²⁺ in Core and Core-Isocrystalline Shell CsPbCl_3 Perovskite Nanocrystals. *Chem. Mater.* **2017**, *29*, 4265–4272.

(610) Das Adhikari, S.; Dutta, A.; Dutta, S. K.; Pradhan, N. Layered Perovskites $\text{L}_2(\text{Pb}_{1-x}\text{Mnx})\text{Cl}_4$ to Mn-Doped CsPbCl_3 Perovskite Platelets. *ACS Energy Lett.* **2018**, *3*, 1247–1253.

(611) Dutta, S. K.; Pradhan, N. Coupled Halide-Deficient and Halide-Rich Reaction System for Doping in Perovskite Armed Nanostructures. *J. Phys. Chem. Lett.* **2019**, *10*, 6788–6793.

(612) Li, F.; Xia, Z.; Gong, Y.; Gu, L.; Liu, Q. Optical Properties of Mn²⁺ Doped Cesium Lead Halide Perovskite Nanocrystals via a Cation–Anion Co-Substitution Exchange Reaction. *J. Mater. Chem. C* **2017**, *5*, 9281–9287.

(613) Huang, G.; Wang, C.; Xu, S.; Zong, S.; Lu, J.; Wang, Z.; Lu, C.; Cui, Y. Postsynthetic Doping of MnCl_2 Molecules into Preformed CsPbBr_3 Perovskite Nanocrystals via a Halide Exchange-Driven Cation Exchange. *Adv. Mater.* **2017**, *29*, 1700095.

(614) De Siena, M. C.; Sommer, D. E.; Creutz, S. E.; Dunham, S. T.; Gamelin, D. R. Spinodal Decomposition during Anion Exchange in Colloidal Mn²⁺-Doped CsPbX_3 (X = Cl, Br) Perovskite Nanocrystals. *Chem. Mater.* **2019**, *31*, 7711–7722.

(615) Parobek, D.; Dong, Y.; Qiao, T.; Rossi, D.; Son, D. H. Photoinduced Anion Exchange in Cesium Lead Halide Perovskite Nanocrystals. *J. Am. Chem. Soc.* **2017**, *139*, 4358–4361.

(616) Xu, K.; Meijerink, A. Tuning Exciton–Mn²⁺ Energy Transfer in Mixed Halide Perovskite Nanocrystals. *Chem. Mater.* **2018**, *30*, S346–S352.

(617) Yuan, X.; Ji, S.; De Siena, M. C.; Fei, L.; Zhao, Z.; Wang, Y.; Li, H.; Zhao, J.; Gamelin, D. R. Photoluminescence Temperature Dependence, Dynamics, and Quantum Efficiencies in Mn²⁺-Doped CsPbCl_3 Perovskite Nanocrystals with Varied Dopant Concentration. *Chem. Mater.* **2017**, *29*, 8003–8011.

(618) Mir, W. J.; Mahor, Y.; Lohar, A.; Jagadeeswararao, M.; Das, S.; Mahamuni, S.; Nag, A. Postsynthesis Doping of Mn and Yb into CsPbX_3 (X = Cl, Br, or I) Perovskite Nanocrystals for Downconversion Emission. *Chem. Mater.* **2018**, *30*, 8170–8178.

(619) Mehetor, S. K.; Ghosh, H.; Hudait, B.; Karan, N. S.; Paul, A.; Baitalik, S.; Pradhan, N. Reversible Color Switching in Dual-Emitting Mn(II)-Doped CsPbBr_3 Perovskite Nanorods: Dilution *versus* Evaporation. *ACS Energy Lett.* **2019**, *4*, 2353–2359.

(620) Parobek, D.; Dong, Y.; Qiao, T.; Son, D. H. Direct Hot-Injection Synthesis of Mn-Doped CsPbBr_3 Nanocrystals. *Chem. Mater.* **2018**, *30*, 2939–2944.

(621) Zou, S.; Liu, Y.; Li, J.; Liu, C.; Feng, R.; Jiang, F.; Li, Y.; Song, J.; Zeng, H.; Hong, M.; Chen, X. Stabilizing Cesium Lead Halide Perovskite Lattice through Mn(II) Substitution for Air-Stable Light-Emitting Diodes. *J. Am. Chem. Soc.* **2017**, *139*, 11443–11450.

(622) Rossi, D.; Parobek, D.; Dong, Y.; Son, D. H. Dynamics of Exciton–Mn Energy Transfer in Mn-Doped CsPbCl_3 Perovskite Nanocrystals. *J. Phys. Chem. C* **2017**, *121*, 17143–17149.

(623) De, A.; Mondal, N.; Samanta, A. Luminescence Tuning and Exciton Dynamics of Mn-Doped CsPbCl_3 Nanocrystals. *Nanoscale* **2017**, *9*, 16722–16727.

(624) Pinchetti, V.; Anand, A.; Akkerman, Q. A.; Sciacca, D.; Lorenzon, M.; Meinardi, F.; Fanciulli, M.; Manna, L.; Brovelli, S. Trap-Mediated Two-Step Sensitization of Manganese Dopants in Perovskite Nanocrystals. *ACS Energy Lett.* **2019**, *4*, 85–93.

(625) Dutta, A.; Pradhan, N. Phase-Stable Red-Emitting CsPbI_3 Nanocrystals: Successes and Challenges. *ACS Energy Lett.* **2019**, *4*, 709–719.

(626) Shen, X.; Zhang, Y.; Kershaw, S. V.; Li, T.; Wang, C.; Zhang, X.; Wang, W.; Li, D.; Wang, Y.; Lu, M.; Zhang, L.; Sun, C.; Zhao, D.; Qin, G.; Bai, X.; Yu, W. W.; Rogach, A. L. Zn-Alloyed CsPbI_3 Nanocrystals for Highly Efficient Perovskite Light-Emitting Devices. *Nano Lett.* **2019**, *19*, 1552–1559.

(627) Yao, J.-S.; Ge, J.; Wang, K.-H.; Zhang, G.; Zhu, B.-S.; Chen, C.; Zhang, Q.; Luo, Y.; Yu, S.-H.; Yao, H.-B. Few-Nanometer-Sized α - CsPbI_3 Quantum Dots Enabled by Strontium Substitution and Iodide Passivation for Efficient Red-Light Emitting Diodes. *J. Am. Chem. Soc.* **2019**, *141*, 2069–2079.

(628) Shi, J.; Li, F.; Yuan, J.; Ling, X.; Zhou, S.; Qian, Y.; Ma, W. Efficient and Stable CsPbI_3 Perovskite Quantum Dots Enabled by *in Situ* Ytterbium Doping for Photovoltaic Applications. *J. Mater. Chem. A* **2019**, *7*, 20936–20944.

(629) Guvenc, C. M.; Yalcinkaya, Y.; Ozen, S.; Sahin, H.; Demir, M. M. Gd³⁺-Doped α - CsPbI_3 Nanocrystals with Better Phase Stability and Optical Properties. *J. Phys. Chem. C* **2019**, *123*, 24865–24872.

(630) Bera, S.; Ghosh, D.; Dutta, A.; Bhattacharyya, S.; Chakraborty, S.; Pradhan, N. Limiting Heterovalent B-Site Doping in CsPbI_3 Nanocrystals: Phase and Optical Stability. *ACS Energy Lett.* **2019**, *4*, 1364–1369.

(631) Lu, M.; Zhang, X.; Bai, X.; Wu, H.; Shen, X.; Zhang, Y.; Zhang, W.; Zheng, W.; Song, H.; Yu, W. W.; Rogach, A. L. Spontaneous Silver Doping and Surface Passivation of CsPbI_3 Perovskite Active Layer Enable Light-Emitting Devices with an External Quantum Efficiency of 11.2%. *ACS Energy Lett.* **2018**, *3*, 1571–1577.

(632) Behera, R. K.; Dutta, A.; Ghosh, D.; Bera, S.; Bhattacharyya, S.; Pradhan, N. Doping the Smallest Shannon Radii Transition Metal Ion Ni(II) for Stabilizing α - CsPbI_3 Perovskite Nanocrystals. *J. Phys. Chem. Lett.* **2019**, *10*, 7916–7921.

(633) Liu, F.; Ding, C.; Zhang, Y.; Kamisaka, T.; Zhao, Q.; Luther, J. M.; Toyoda, T.; Hayase, S.; Minemoto, T.; Yoshino, K.; Zhang, B.; Dai, S.; Jiang, J.; Tao, S.; Shen, Q. GeI_2 Additive for High Optoelectronic Quality CsPbI_3 Quantum Dots and Their Application in Photovoltaic Devices. *Chem. Mater.* **2019**, *31*, 798–807.

(634) Xu, L.; Yuan, S.; Zeng, H.; Song, J. A Comprehensive Review of Doping in Perovskite Nanocrystals/Quantum Dots: Evolution of Structure, Electronics, Optics, and Light-Emitting Diodes. *Mater. Today Nano* **2019**, *6*, 100036.

(635) Saliba, M.; Matsui, T.; Domanski, K.; Seo, J.-Y.; Ummadisingu, A.; Zakeeruddin, S. M.; Correa-Baena, J.-P.; Tress, W. R.; Abate, A.; Hagfeldt, A.; Grätzel, M. Incorporation of Rubidium

Cations into Perovskite Solar Cells Improves Photovoltaic Performance. *Science* **2016**, *354*, 206–209.

(636) Shi, Y.; Xi, J.; Lei, T.; Yuan, F.; Dai, J.; Ran, C.; Dong, H.; Jiao, B.; Hou, X.; Wu, Z. Rubidium Doping for Enhanced Performance of Highly Efficient Formamidinium-Based Perovskite Light-Emitting Diodes. *ACS Appl. Mater. Interfaces* **2018**, *10*, 9849–9857.

(637) Li, S.; Shi, Z.; Zhang, F.; Wang, L.; Ma, Z.; Yang, D.; Yao, Z.; Wu, D.; Xu, T.-T.; Tian, Y.; Zhang, Y.; Shan, C.; Li, X. J. Sodium Doping-Enhanced Emission Efficiency and Stability of CsPbBr_3 Nanocrystals for White Light-Emitting Devices. *Chem. Mater.* **2019**, *31*, 3917–3928.

(638) Binyamin, T.; Pedesseau, L.; Remennik, S.; Sawahreh, A.; Even, J.; Etgar, L. Fully Inorganic Mixed Cation Lead Halide Perovskite Nanoparticles: A Study at the Atomic Level. *Chem. Mater.* **2020**, *32*, 1467–1474.

(639) Xiao, J.-W.; Liang, Y.; Zhang, S.; Zhao, Y.; Li, Y.; Chen, Q. Stabilizing RbPbBr_3 Perovskite Nanocrystals through Cs^+ Substitution. *Chem. - Eur. J.* **2019**, *25*, 2597–2603.

(640) Todorović, P.; Ma, D.; Chen, B.; Quintero-Bermudez, R.; Saidaminov, M. I.; Dong, Y.; Lu, Z.-H.; Sargent, E. H. Spectrally Tunable and Stable Electroluminescence Enabled by Rubidium Doping of CsPbBr_3 Nanocrystals. *Adv. Opt. Mater.* **2019**, *7*, 1901440.

(641) Amgar, D.; Binyamin, T.; Uvarov, V.; Etgar, L. Near Ultra-Violet to Mid-Visible Band Gap Tuning of Mixed Cation $\text{Rb}_x\text{Cs}_{1-x}\text{PbX}_3$ (X = Cl or Br) Perovskite Nanoparticles. *Nanoscale* **2018**, *10*, 6060–6068.

(642) Lin, Y.-H.; Qiu, Z.-H.; Wang, S.-H.; Zhang, X.-H.; Wu, S.-F. All-Inorganic $\text{Rb}_x\text{Cs}_{1-x}\text{PbBrI}_2$ Perovskite Nanocrystals with Wavelength-Tunable Properties for Red Light-Emitting. *Inorg. Chem. Commun.* **2019**, *103*, 47–52.

(643) Kubicki, D. J.; Prochowicz, D.; Hofstetter, A.; Zakeeruddin, S. M.; Grätzel, M.; Emsley, L. Phase Segregation in Cs-, Rb- and K-Doped Mixed-Cation $(\text{MA})_x(\text{FA})_{1-x}\text{PbI}_3$ Hybrid Perovskites from Solid-State NMR. *J. Am. Chem. Soc.* **2017**, *139*, 14173–14180.

(644) Chen, H.; Fan, L.; Zhang, R.; Liu, W.; Zhang, Q.; Guo, R.; Zhuang, S.; Wang, L. Sodium Ion Modifying *in Situ* Fabricated CsPbBr_3 Nanoparticles for Efficient Perovskite Light Emitting Diodes. *Adv. Opt. Mater.* **2019**, *7*, 1900747.

(645) Ronda, C., Ed. *Luminescence: From Theory to Applications*; Wiley-VCH: Weinheim, Germany, 2008.

(646) Blasse, G.; Grabmaier, B. C. *Luminescent Materials*; Springer-Verlag: Berlin, Germany, 1994.

(647) Zhou, D.; Liu, D.; Pan, G.; Chen, X.; Li, D.; Xu, W.; Bai, X.; Song, H. Cerium and Ytterbium Codoped Halide Perovskite Quantum Dots: A Novel and Efficient Downconverter for Improving the Performance of Silicon Solar Cells. *Adv. Mater.* **2017**, *29*, 1704149.

(648) Yao, J.-S.; Ge, J.; Han, B.-N.; Wang, K.-H.; Yao, H.-B.; Yu, H.-L.; Li, J.-H.; Zhu, B.-S.; Song, J.-Z.; Chen, C.; Zhang, Q.; Zeng, H.-B.; Luo, Y.; Yu, S.-H. Ce³⁺-Doping to Modulate Photoluminescence Kinetics for Efficient CsPbBr_3 Nanocrystals Based Light-Emitting Diodes. *J. Am. Chem. Soc.* **2018**, *140*, 3626–3634.

(649) Li, Q.; Liu, Y.; Chen, P.; Hou, J.; Sun, Y.; Zhao, G.; Zhang, N.; Zou, J.; Xu, J.; Fang, Y.; Dai, N. Excitonic Luminescence Engineering in Tervalent-Europium-Doped Cesium Lead Halide Perovskite Nanocrystals and Their Temperature-Dependent Energy Transfer Emission Properties. *J. Phys. Chem. C* **2018**, *122*, 29044–29050.

(650) Milstein, T.; Kroupa, D. M.; Gamelin, D. R. Picosecond Quantum Cutting Generates Photoluminescence Quantum Yields over 100% in Ytterbium-Doped CsPbCl_3 Nanocrystals. *Nano Lett.* **2018**, *18*, 3792–3799.

(651) Zheng, W.; Huang, P.; Gong, Z.; Tu, D.; Xu, J.; Zou, Q.; Li, R.; You, W.; Bünzli, J.-C. G.; Chen, X. Near-Infrared-Triggered Photon Upconversion Tuning in All-Inorganic Cesium Lead Halide Perovskite Quantum Dots. *Nat. Commun.* **2018**, *9*, 3462.

(652) Pan, G.; Bai, X.; Xu, W.; Chen, X.; Zhou, D.; Zhu, J.; Shao, H.; Zhai, Y.; Dong, B.; Xu, L.; Song, H. Impurity Ions Co-Doped Cesium Lead Halide Perovskite Nanocrystals with Bright White Light Emission toward Ultraviolet–White Light-Emitting Diode. *ACS Appl. Mater. Interfaces* **2018**, *10*, 39040–39048.

(653) Zhang, X.; Zhang, Y.; Zhang, X.; Yin, W.; Wang, Y.; Wang, H.; Lu, M.; Li, Z.; Gu, Z.; Yu, W. W. Yb³⁺ and Yb³⁺/Er³⁺ Doping for Near-Infrared Emission and Improved Stability of CsPbCl_3 Nanocrystals. *J. Mater. Chem. C* **2018**, *6*, 10101–10105.

(654) Zhou, L.; Liu, T.; Zheng, J.; Yu, K.; Yang, F.; Wang, N.; Zuo, Y.; Liu, Z.; Xue, C.; Li, C.; Cheng, B.; Wang, Q. Dual-Emission and Two Charge-Transfer States in Ytterbium-Doped Cesium Lead Halide Perovskite Solid Nanocrystals. *J. Phys. Chem. C* **2018**, *122*, 26825–26834.

(655) Luo, X.; Ding, T.; Liu, X.; Liu, Y.; Wu, K. Quantum-Cutting Luminescent Solar Concentrators Using Ytterbium-Doped Perovskite Nanocrystals. *Nano Lett.* **2019**, *19*, 338–341.

(656) Cohen, T. A.; Milstein, T. J.; Kroupa, D. M.; MacKenzie, J. D.; Luscombe, C. K.; Gamelin, D. R. Quantum-Cutting Yb³⁺-Doped Perovskite Nanocrystals for Monolithic Bilayer Luminescent Solar Concentrators. *J. Mater. Chem. A* **2019**, *7*, 9279–9288.

(657) Crane, M. J.; Kroupa, D. M.; Gamelin, D. R. Detailed-Balance Analysis of $\text{Yb}^{3+}:\text{CsPb}(\text{Cl}_{1-x}\text{Br}_x)_3$ Quantum-Cutting Layers for High-Efficiency Photovoltaics under Real-World Conditions. *Energy Environ. Sci.* **2019**, *12*, 2486–2495.

(658) Erickson, C. S.; Crane, M. J.; Milstein, T. J.; Gamelin, D. R. Photoluminescence Saturation in Quantum-Cutting Yb³⁺-Doped $\text{CsPb}(\text{Cl}_{1-x}\text{Br}_x)_3$ Perovskite Nanocrystals: Implications for Solar Downconversion. *J. Phys. Chem. C* **2019**, *123*, 12474–12484.

(659) Milstein, T. J.; Klucher, K. T.; Kroupa, D. M.; Erickson, C. S.; De Yoreo, J. J.; Gamelin, D. R. Anion Exchange and the Quantum-Cutting Energy Threshold in Ytterbium-Doped $\text{CsPb}(\text{Cl}_{1-x}\text{Br}_x)_3$ Perovskite Nanocrystals. *Nano Lett.* **2019**, *19*, 1931–1937.

(660) García-Lojo, D.; Núñez-Sánchez, S.; Gómez-Gráña, S.; Grzelczak, M.; Pastoriza-Santos, I.; Pérez-Juste, J.; Liz-Marzáñ, L. M. Plasmonic Supercrystals. *Acc. Chem. Res.* **2019**, *52*, 1855–1864.

(661) Zhou, D.; Sun, R.; Xu, W.; Ding, N.; Li, D.; Chen, X.; Pan, G.; Bai, X.; Song, H. Impact of Host Composition, Codoping, or Tridoping on Quantum-Cutting Emission of Ytterbium in Halide Perovskite Quantum Dots and Solar Cell Applications. *Nano Lett.* **2019**, *19*, 6904–6913.

(662) Luo, B.; Li, F.; Xu, K.; Guo, Y.; Liu, Y.; Xia, Z.; Zhang, J. Z. B-Site Doped Lead Halide Perovskites: Synthesis, Band Engineering, Photophysics, and Light Emission Applications. *J. Mater. Chem. C* **2019**, *7*, 2781–2808.

(663) Pan, G.; Bai, X.; Yang, D.; Chen, X.; Jing, P.; Qu, S.; Zhang, L.; Zhou, D.; Zhu, J.; Xu, W.; Dong, B.; Song, H. Doping Lanthanide into Perovskite Nanocrystals: Highly Improved and Expanded Optical Properties. *Nano Lett.* **2017**, *17*, 8005–8011.

(664) Heer, S.; Koempe, K.; Güdel, H.-U.; Haase, M. Highly Efficient Multicolour Upconversion Emission in Transparent Colloids of Lanthanide-Doped NaYF_4 Nanocrystals. *Adv. Mater.* **2004**, *16*, 2102–2105.

(665) Wang, F.; Liu, X. Recent Advances in the Chemistry of Lanthanide-Doped Upconversion Nanocrystals. *Chem. Soc. Rev.* **2009**, *38*, 976–989.

(666) Haase, M.; Schäfer, H. Upconverting Nanoparticles. *Angew. Chem., Int. Ed.* **2011**, *50*, 5808–5829.

(667) Wegh, R. T.; Donker, H.; Oskam, K. D.; Meijerink, A. Visible Quantum Cutting in $\text{LiGdF}_4:\text{Eu}^{3+}$ through Downconversion. *Science* **1999**, *283*, 663–666.

(668) van der Ende, B. M.; Aarts, L.; Meijerink, A. Lanthanide Ions as Spectral Converters for Solar Cells. *Phys. Chem. Chem. Phys.* **2009**, *11*, 11081–11095.

(669) Liu, T.-C.; Zhang, G.; Qiao, X.; Wang, J.; Seo, H. J.; Tsai, D.-P.; Liu, R.-S. Near-Infrared Quantum Cutting Platform in Thermally Stable Phosphate Phosphors for Solar Cells. *Inorg. Chem.* **2013**, *52*, 7352–7357.

(670) Chen, D.; Zhou, S.; Fang, G.; Chen, X.; Zhong, J. Fast Room-Temperature Cation Exchange Synthesis of Mn-Doped CsPbCl_3 Nanocrystals Driven by Dynamic Halogen Exchange. *ACS Appl. Mater. Interfaces* **2018**, *10*, 39872–39878.

(671) Erickson, C. S.; Bradshaw, L. R.; McDowall, S.; Gilbertson, J. D.; Gamelin, D. R.; Patrick, D. L. Zero-Reabsorption Doped-Nanocrystal Luminescent Solar Concentrators. *ACS Nano* **2014**, *8*, 3461–3467.

(672) Bradshaw, L. R.; Knowles, K. E.; McDowall, S.; Gamelin, D. R. Nanocrystals for Luminescent Solar Concentrators. *Nano Lett.* **2015**, *15*, 1315–1323.

(673) Knowles, K. E.; Kilburn, T. B.; Alzate, D. G.; McDowall, S.; Gamelin, D. R. Bright CuInS₂/CdS Nanocrystal Phosphors for High-Gain Full-Spectrum Luminescent Solar Concentrators. *Chem. Commun.* **2015**, *51*, 9129–9132.

(674) Meinardi, F.; McDaniel, H.; Carulli, F.; Colombo, A.; Velizhanin, K. A.; Makarov, N. S.; Simonutti, R.; Klimov, V. I.; Brovelli, S. Highly Efficient Large-Area Colourless Luminescent Solar Concentrators Using Heavy-Metal-Free Colloidal Quantum Dots. *Nat. Nanotechnol.* **2015**, *10*, 878–885.

(675) Sumner, R.; Eiselt, S.; Kilburn, T. B.; Erickson, C.; Carlson, B.; Gamelin, D. R.; McDowall, S.; Patrick, D. L. Analysis of Optical Losses in High-Efficiency CuInS₂-Based Nanocrystal Luminescent Solar Concentrators: Balancing Absorption *versus* Scattering. *J. Phys. Chem. C* **2017**, *121*, 3252–3260.

(676) Bergren, M. R.; Makarov, N. S.; Ramasamy, K.; Jackson, A.; Guglielmetti, R.; McDaniel, H. High-Performance CuInS₂ Quantum Dot Laminated Glass Luminescent Solar Concentrators for Windows. *ACS Energy Lett.* **2018**, *3*, 520–525.

(677) Boles, M. A.; Engel, M.; Talapin, D. V. Self-Assembly of Colloidal Nanocrystals: From Intricate Structures to Functional Materials. *Chem. Rev.* **2016**, *116*, 11220–11289.

(678) Weller, H. Synthesis and Self-Assembly of Colloidal Nanoparticles. *Philos. Trans. R. Soc., A* **2003**, *361*, 229–240.

(679) Shevchenko, E. V.; Talapin, D. V.; Kotov, N. A.; O'Brien, S.; Murray, C. B. Structural Diversity in Binary Nanoparticle Superlattices. *Nature* **2006**, *439*, 55–59.

(680) Redl, F. X.; Cho, K. S.; Murray, C. B.; O'Brien, S. Three-Dimensional Binary Superlattices of Magnetic Nanocrystals and Semiconductor Quantum Dots. *Nature* **2003**, *423*, 968–971.

(681) Soetan, N.; Erwin, W. R.; Tonigan, A. M.; Walker, D. G.; Bardhan, R. Solvent-Assisted Self-Assembly of CsPbBr₃ Perovskite Nanocrystals into One-Dimensional Superlattice. *J. Phys. Chem. C* **2017**, *121*, 18186–18194.

(682) Liu, Y.; Siron, M.; Lu, D.; Yang, J.; dos Reis, R.; Cui, F.; Gao, M.; Lai, M.; Lin, J.; Kong, Q.; Lei, T.; Kang, J.; Jin, J.; Ciston, J.; Yang, P. Self-Assembly of Two-Dimensional Perovskite Nanosheet Building Blocks into Ordered Ruddlesden–Popper Perovskite Phase. *J. Am. Chem. Soc.* **2019**, *141*, 13028–13032.

(683) Patra, B. K.; Agrawal, H.; Zheng, J.-Y.; Zha, X.; Travasset, A.; Garnett, E. C. Close-Packed Ultrasmooth Self-Assembled Monolayer of CsPbBr₃ Perovskite Nanocubes. *ACS Appl. Mater. Interfaces* **2020**, *12*, 31764–31769.

(684) van der Burgt, J. S.; Geuchies, J. J.; van der Meer, B.; Vanrompay, H.; Zanaga, D.; Zhang, Y.; Albrecht, W.; Petukhov, A. V.; Filion, L.; Bals, S.; Swart, I.; Vanmaekelbergh, D. Cuboidal Supraparticles Self-Assembled from Cubic CsPbBr₃ Perovskite Nanocrystals. *J. Phys. Chem. C* **2018**, *122*, 15706–15712.

(685) Xin, B.; Pak, Y.; Mitra, S.; Almalawi, D.; Alwadai, N.; Zhang, Y.; Roqan, I. S. Self-Patterned CsPbBr₃ Nanocrystals for High-Performance Optoelectronics. *ACS Appl. Mater. Interfaces* **2019**, *11*, 5223–5231.

(686) Mehetor, S. K.; Ghosh, H.; Pradhan, N. Blue-Emitting CsPbBr₃ Perovskite Quantum Rods and Their Wide-Area 2D Self-Assembly. *ACS Energy Lett.* **2019**, *4*, 1437–1442.

(687) Wang, K.-H.; Yang, J.-N.; Ni, Q.-K.; Yao, H.-B.; Yu, S.-H. Metal Halide Perovskite Supercrystals: Gold–Bromide Complex Triggered Assembly of CsPbBr₃ Nanocubes. *Langmuir* **2018**, *34*, 595–602.

(688) Vila-Liarte, D.; Feil, M. W.; Manzi, A.; Garcia-Pomar, J. L.; Huang, H.; Döblinger, M.; Liz-Marzán, L. M.; Feldmann, J.; Polavarapu, L.; Mihi, A. Templated-Assembly of CsPbBr₃ Perovskite Nanocrystals into 2D Photonic Supercrystals with Amplified Spontaneous Emission. *Angew. Chem., Int. Ed.* **2020**, *59*, 17750–17756.

(689) Krieg, F.; Sercel, P. C.; Burian, M.; Andrusiv, H.; Bodnarchuk, M. I.; Stöferle, T.; Mahrt, R. F.; Naumenko, D.; Amenitsch, H.; Rainò, G.; Kovalenko, M. V. Monodisperse Long-Chain Sulfobetaine-Capped CsPbBr₃ Nanocrystals and Their Superfluorescent Assemblies. *ACS Cent. Sci.* **2021**, *7*, 135–144.

(690) Prasad, B. L. V.; Sorensen, C. M.; Klabunde, K. J. Gold Nanoparticle Superlattices. *Chem. Soc. Rev.* **2008**, *37*, 1871–1883.

(691) Motte, L.; Billoudet, F.; Lacaze, E.; Pileni, M.-P. Self-Organization of Size-Selected, Nanoparticles into Three-Dimensional Superlattices. *Adv. Mater.* **1996**, *8*, 1018–1020.

(692) Toso, S.; Baranov, D.; Giannini, C.; Marras, S.; Manna, L. Wide-Angle X-ray Diffraction Evidence of Structural Coherence in CsPbBr₃ Nanocrystal Superlattices. *ACS Mater. Lett.* **2019**, *1*, 272–276.

(693) Zhou, C.; Zhong, Y.; Dong, H.; Zheng, W.; Tan, J.; Jie, Q.; Pan, A.; Zhang, L.; Xie, W. Cooperative Excitonic Quantum Ensemble in Perovskite-Assembly Superlattice Microcavities. *Nat. Commun.* **2020**, *11*, 329.

(694) Pan, A.; Jurow, M.; Zhao, Y.; Qiu, F.; Liu, Y.; Yang, J.; Urban, J. J.; He, L.; Liu, Y. Templated Self-Assembly of One-Dimensional CsPbX₃ Perovskite Nanocrystal Superlattices. *Nanoscale* **2017**, *9*, 17688–17693.

(695) Wang, K.; Xing, G.; Song, Q.; Xiao, S. Micro- and Nanostructured Lead Halide Perovskites: From Materials to Integrations and Devices. *Adv. Mater.* **2021**, *33*, 2000306.

(696) Lin, C. H.; Zeng, Q.; Lafalce, E.; Yu, S.; Smith, M. J.; Yoon, Y. J.; Chang, Y.; Jiang, Y.; Lin, Z.; Vardeny, Z. V.; Tsukruk, V. V. Large-Area Lasing and Multicolor Perovskite Quantum Dot Patterns. *Adv. Opt. Mater.* **2018**, *6*, 1800474.

(697) Liu, H.; Siron, M.; Gao, M.; Lu, D.; Bekenstein, Y.; Zhang, D.; Dou, L.; Alivisatos, A. P.; Yang, P. Lead Halide Perovskite Nanowires Stabilized by Block Copolymers for Langmuir–Blodgett Assembly. *Nano Res.* **2020**, *13*, 1453–1458.

(698) Gladman, A. S.; Matsumoto, E. A.; Nuzzo, R. G.; Mahadevan, L.; Lewis, J. A. Biomimetic 4D Printing. *Nat. Mater.* **2016**, *15*, 413–418.

(699) Zhou, N. J.; Bekenstein, Y.; Eisler, C. N.; Zhang, D. D.; Schwartzberg, A. M.; Yang, P. D.; Alivisatos, A. P.; Lewis, J. A. Perovskite Nanowire-Block Copolymer Composites with Digitally Programmable Polarization Anisotropy. *Sci. Adv.* **2019**, *5*, eaav8141.

(700) Zhu, F.; Men, L.; Guo, Y.; Zhu, Q.; Bhattacharjee, U.; Goodwin, P. M.; Petrich, J. W.; Smith, E. A.; Vela, J. Shape Evolution and Single Particle Luminescence of Organometal Halide Perovskite Nanocrystals. *ACS Nano* **2015**, *9*, 2948–2959.

(701) Shamsi, J.; Dang, Z.; Bianchini, P.; Canale, C.; Di Stasio, F.; Brescia, R.; Prato, M.; Manna, L. Colloidal Synthesis of Quantum Confined Single Crystal CsPbBr₃ Nanosheets with Lateral Size Control up to the Micrometer Range. *J. Am. Chem. Soc.* **2016**, *138*, 7240–7243.

(702) Yu, Y.; Zhang, D.; Kisielowski, C.; Dou, L.; Kornienko, N.; Bekenstein, Y.; Wong, A. B.; Alivisatos, A. P.; Yang, P. Atomic Resolution Imaging of Halide Perovskites. *Nano Lett.* **2016**, *16*, 7530–7535.

(703) Dang, Z.; Shamsi, J.; Akkerman, Q. A.; Imran, M.; Bertoni, G.; Brescia, R.; Manna, L. Low-Temperature Electron Beam-Induced Transformations of Cesium Lead Halide Perovskite Nanocrystals. *ACS Omega* **2017**, *2*, 5660–5665.

(704) Udayabaskararao, T.; Houben, L.; Cohen, H.; Menahem, M.; Pinkas, I.; Avram, L.; Wolf, T.; Teitelboim, A.; Leskes, M.; Yaffe, O.; Oron, D.; Kazes, M. A Mechanistic Study of Phase Transformation in Perovskite Nanocrystals Driven by Ligand Passivation. *Chem. Mater.* **2018**, *30*, 84–93.

(705) Brennan, M. C.; Kuno, M.; Rouvimov, S. Crystal Structure of Individual CsPbBr₃ Perovskite Nanocubes. *Inorg. Chem.* **2019**, *58*, 1555–1560.

(706) Shen, Q.; Ripolles, T. S.; Even, J.; Ogomi, Y.; Nishinaka, K.; Izuishi, T.; Nakazawa, N.; Zhang, Y.; Ding, C.; Liu, F.; Toyoda, T.;

Yoshino, K.; Minemoto, T.; Katayama, K.; Hayase, S. Slow Hot Carrier Cooling in Cesium Lead Iodide Perovskites. *Appl. Phys. Lett.* **2017**, *111*, 153903.

(707) Morrell, M. V.; He, X.; Luo, G.; Thind, A. S.; White, T. A.; Hachtel, J. A.; Borisevich, A. Y.; Idrobo, J.-C.; Mishra, R.; Xing, Y. Significantly Enhanced Emission Stability of CsPbBr_3 Nanocrystals via Chemically Induced Fusion Growth for Optoelectronic Devices. *ACS Appl. Nano Mater.* **2018**, *1*, 6091–6098.

(708) Song, K.; Liu, L.; Zhang, D.; Hautzinger, M. P.; Jin, S.; Han, Y. Atomic-Resolution Imaging of Halide Perovskites Using Electron Microscopy. *Adv. Energy Mater.* **2020**, *10*, 1904006.

(709) Zhang, D.; Zhu, Y.; Liu, L.; Ying, X.; Hsiung, C.-E.; Sougrat, R.; Li, K.; Han, Y. Atomic-Resolution Transmission Electron Microscopy of Electron Beam–Sensitive Crystalline Materials. *Science* **2018**, *359*, 675–679.

(710) Li, Y.; Zhou, W.; Li, Y.; Huang, W.; Zhang, Z.; Chen, G.; Wang, H.; Wu, G.-H.; Rolston, N.; Vila, R.; Chiu, W.; Cui, Y. Unravelling Degradation Mechanisms and Atomic Structure of Organic-Inorganic Halide Perovskites by Cryo-EM. *Joule* **2019**, *3*, 2854–2866.

(711) Van Aert, S.; Verbeeck, J.; Erni, R.; Bals, S.; Luysberg, M.; Dyck, D. V.; Tendeloo, G. V. Quantitative Atomic Resolution Mapping Using High-Angle Annular Dark Field Scanning Transmission Electron Microscopy. *Ultramicroscopy* **2009**, *109*, 1236–1244.

(712) De Backer, A.; van den Bos, K. H. W.; Van den Broek, W.; Sijbers, J.; Van Aert, S. StatSTEM: An Efficient Approach for Accurate and Precise Model-Based Quantification of Atomic Resolution Electron Microscopy Images. *Ultramicroscopy* **2016**, *171*, 104–116.

(713) Akkerman, Q. A.; Bladt, E.; Petralanda, U.; Dang, Z.; Sartori, E.; Baranov, D.; Abdelhady, A. L.; Infante, I.; Bals, S.; Manna, L. Fully Inorganic Ruddlesden–Popper Double Cl–I and Triple Cl–Br–I Lead Halide Perovskite Nanocrystals. *Chem. Mater.* **2019**, *31*, 2182–2190.

(714) Polavarapu, L.; Nickel, B.; Feldmann, J.; Urban, A. S. Advances in Quantum-Confining Perovskite Nanocrystals for Optoelectronics. *Adv. Energy Mater.* **2017**, *7*, 1700267.

(715) Yuan, M.; Quan, L. N.; Comin, R.; Walters, G.; Sabatini, R.; Voznyy, O.; Hoogland, S.; Zhao, Y.; Beauregard, E. M.; Kanjanaboons, P.; Lu, Z.; Kim, D. H.; Sargent, E. H. Perovskite Energy Funnels for Efficient Light-Emitting Diodes. *Nat. Nanotechnol.* **2016**, *11*, 872–877.

(716) Konstantatos, G.; Sargent, E. H. Nanostructured Materials for Photon Detection. *Nat. Nanotechnol.* **2010**, *5*, 391–400.

(717) Petrus, M. L.; Schlipf, J.; Li, C.; Gujar, T. P.; Giesbrecht, N.; Müller-Buschbaum, P.; Thelakkat, M.; Bein, T.; Hüttner, S.; Docampo, P. Capturing the Sun: A Review of the Challenges and Perspectives of Perovskite Solar Cells. *Adv. Energy Mater.* **2017**, *7*, 1700264.

(718) Mundt, L. E.; Schelhas, L. T. Structural Evolution During Perovskite Crystal Formation and Degradation: *in Situ* and Operando X-Ray Diffraction Studies. *Adv. Energy Mater.* **2020**, *10*, 1903074.

(719) Alsari, M.; Bikondoa, O.; Bishop, J.; Abdi-Jalebi, M.; Ozer, L. Y.; Hampton, M.; Thompson, P.; T. Hörantner, M.; Mahesh, S.; Greenland, C.; Macdonald, J. E.; Palmisano, G.; Snaith, H. J.; Lidzey, D. G.; Stranks, S. D.; Friend, R. H.; Lilliu, S. *In Situ* Simultaneous Photovoltaic and Structural Evolution of Perovskite Solar Cells during Film Formation. *Energy Environ. Sci.* **2018**, *11*, 383–393.

(720) Fransishyn, K. M.; Kundu, S.; Kelly, T. L. Elucidating the Failure Mechanisms of Perovskite Solar Cells in Humid Environments Using *in Situ* Grazing-Incidence Wide-Angle X-Ray Scattering. *ACS Energy Lett.* **2018**, *3*, 2127–2133.

(721) Bhaway, S. M.; Qiang, Z.; Xia, Y.; Xia, X.; Lee, B.; Yager, K. G.; Zhang, L.; Kisslinger, K.; Chen, Y. M.; Liu, K.; Zhu, Y.; Vogt, B. D. Operando Grazing Incidence Small-Angle X-Ray Scattering/X-ray Diffraction of Model Ordered Mesoporous Lithium-Ion Battery Anodes. *ACS Nano* **2017**, *11*, 1443–1454.

(722) Yang, D.; Löhner, F. C.; Körstgens, V.; Schreiber, A.; Cao, B.; Bernstorff, S.; Müller-Buschbaum, P. in Operando GISAXS and GIWAXS Stability Study of Organic Solar Cells Based on PffBT4T-2OD:PC₇1BM with and without Solvent Additive. *Adv. Sci.* **2020**, *7*, 2001117.

(723) Schlipf, J.; Müller-Buschbaum, P. Structure of Organometal Halide Perovskite Films as Determined with Grazing-Incidence X-Ray Scattering Methods. *Adv. Energy Mater.* **2017**, *7*, 1700131.

(724) Li, T.; Senesi, A. J.; Lee, B. Small Angle X-Ray Scattering for Nanoparticle Research. *Chem. Rev.* **2016**, *116*, 11128–80.

(725) Müller-Buschbaum, P. The Active Layer Morphology of Organic Solar Cells Probed with Grazing Incidence Scattering Techniques. *Adv. Mater.* **2014**, *26*, 7692–709.

(726) Tsybulya, S.; Yatsenko, D. X-Ray Diffraction Analysis of Ultradisperse Systems: The Debye Formula. *J. Struct. Chem.* **2012**, *53*, 150–165.

(727) Müller-Buschbaum, P. A Basic Introduction to Grazing Incidence Small-Angle X-ray Scattering. *Applications of Synchrotron Light to Scattering and Diffraction in Materials and Life Sciences*; Springer: Berlin, 2009; Vol. 776, pp 61–89.

(728) Müller-Buschbaum, P. Structure Determination in Thin Film Geometry Using Grazing Incidence Small-Angle Scattering. In *Polymer Surfaces and Interfaces*; Springer: Berlin, 2008; pp 17–46.

(729) Putnam, C. D.; Hammel, M.; Hura, G. L.; Tainer, J. A. X-Ray Solution Scattering (SAXS) Combined with Crystallography and Computation: Defining Accurate Macromolecular Structures, Conformations and Assemblies in Solution. *Q. Rev. Biophys.* **2007**, *40*, 191–285.

(730) Hexemer, A.; Müller-Buschbaum, P. Advanced Grazing-Incidence Techniques for Modern Soft-Matter Materials Analysis. *IUCrJ* **2015**, *2*, 106–125.

(731) Müller-Buschbaum, P. Grazing Incidence Small-Angle X-Ray Scattering: An Advanced Scattering Technique for the Investigation of Nanostructured Polymer Films. *Anal. Bioanal. Chem.* **2003**, *376*, 3–10.

(732) Gordon, T. R.; Diroll, B. T.; Paik, T.; Doan-Nguyen, V. V. T.; Gaulding, E. A.; Murray, C. B. Characterization of Shape and Monodispersity of Anisotropic Nanocrystals through Atomistic X-Ray Scattering Simulation. *Chem. Mater.* **2015**, *27*, 2502–2506.

(733) Yager, K. G.; Zhang, Y.; Lu, F.; Gang, O. Periodic Lattices of Arbitrary Nano-Objects: Modeling and Applications for Self-Assembled Systems. *J. Appl. Crystallogr.* **2014**, *47*, 118–129.

(734) Brentano, J. Focussing Method of Crystal Powder Analysis by X-Rays. *Proc. Phys. Soc. (London)* **1924**, *37*, 184.

(735) Sharma, A. K.; Bansal, P.; Nim, G. K.; Kar, P. Essential Amino Acid-Enabled Lead Bromide Perovskite Nanocrystals with High Stability. *Part. Part. Syst. Charact.* **2019**, *36*, 1900328.

(736) Boote, B. W.; Andaraarachchi, H. P.; Rosales, B. A.; Blome-Fernandez, R.; Zhu, F.; Reichert, M. D.; Santra, K.; Li, J.; Petrich, J. W.; Vela, J.; Smith, E. A. Unveiling the Photo- and Thermal-Stability of Cesium Lead Halide Perovskite Nanocrystals. *ChemPhysChem* **2019**, *20*, 2647–2656.

(737) Tiensuu, V. H.; Ergun, S.; Alexander, L. E. X-Ray Diffraction from Small Crystallites. *J. Appl. Phys.* **1964**, *35*, 1718–1720.

(738) Kumpf, C.; Neder, R. B.; Niederdraen, F.; Luczak, P.; Stahl, A.; Scheuermann, M.; Joshi, S.; Kulkarni, S. K.; Barglik-Chory, C.; Heske, C.; Umbach, E. Structure Determination of CdS and ZnS Nanoparticles: Direct Modeling of Synchrotron-Radiation Diffraction Data. *J. Chem. Phys.* **2005**, *123*, 224707.

(739) Yu, J. C.; Lee, A.-Y.; Kim, D. B.; Jung, E. D.; Kim, D. W.; Song, M. H. Enhancing the Performance and Stability of Perovskite Nanocrystal Light-Emitting Diodes with a Polymer Matrix. *Adv. Mater. Technol.* **2017**, *2*, 1700003.

(740) Goldschmidt, V. M. Die Gesetze der Krystallochemie. *Naturwissenschaften* **1926**, *14*, 477–485.

(741) Li, J.; Wang, L.; Yuan, X.; Bo, B.; Li, H.; Zhao, J.; Gao, X. Ultraviolet Light Induced Degradation of Luminescence in CsPbBr_3 Perovskite Nanocrystals. *Mater. Res. Bull.* **2018**, *102*, 86–91.

(742) Zhu, H.; Cai, T.; Que, M.; Song, J. P.; Rubenstein, B. M.; Wang, Z.; Chen, O. Pressure-Induced Phase Transformation and Band-Gap Engineering of Formamidinium Lead Iodide Perovskite Nanocrystals. *J. Phys. Chem. Lett.* **2018**, *9*, 4199–4205.

(743) Quan, L. N.; Yuan, M.; Comin, R.; Voznyy, O.; Beauregard, E. M.; Hoogland, S.; Buin, A.; Kirmani, A. R.; Zhao, K.; Amassian, A.; Kim, D. H.; Sargent, E. H. Ligand-Stabilized Reduced-Dimensionality Perovskites. *J. Am. Chem. Soc.* **2016**, *138*, 2649–55.

(744) Chen, W.; Tang, H.; Li, N.; Scheel, M. A.; Xie, Y.; Li, D.; Korstgens, V.; Schwartzkopf, M.; Roth, S. V.; Wang, K.; Sun, X. W.; Müller-Buschbaum, P. Colloidal PbS Quantum Dot Stacking Kinetics During Deposition via Printing. *Nanoscale Horiz.* **2020**, *5*, 880–885.

(745) De Caro, L.; Scattarella, F.; Altamura, D.; Arciniegas, M. P.; Siliqi, D.; Manna, L.; Giannini, C. X-ray Ptychographic Mode of Self-Assembled CdSe/CdS Octapod-Shaped Nanocrystals in Thick Polymers. *J. Appl. Crystallogr.* **2020**, *53*, 741–747.

(746) Sasaki, E.; Dragoman, R. M.; Mantri, S.; Dirin, D. N.; Kovalenko, M. V.; Hilvert, D. Self-Assembly of Proteinaceous Shells around Positively Charged Gold Nanomaterials Enhances Colloidal Stability in High-Ionic-Strength Buffers. *ChemBioChem* **2020**, *21*, 74–79.

(747) Liao, Y.; Liu, H.; Zhou, W.; Yang, D.; Shang, Y.; Shi, Z.; Li, B.; Jiang, X.; Zhang, L.; Quan, L. N.; Quintero-Bermudez, R.; Sutherland, B. R.; Mi, Q.; Sargent, E. H.; Ning, Z. Highly Oriented Low-Dimensional Tin Halide Perovskites with Enhanced Stability and Photovoltaic Performance. *J. Am. Chem. Soc.* **2017**, *139*, 6693–6699.

(748) Tao, A. R.; Habas, S.; Yang, P. Shape Control of Colloidal Metal Nanocrystals. *Small* **2008**, *4*, 310–325.

(749) Chen, W.; Zhong, J.; Li, J.; Saxena, N.; Kreuzer, L. P.; Liu, H.; Song, L.; Su, B.; Yang, D.; Wang, K.; Schlipp, J.; Korstgens, V.; He, T.; Wang, K.; Müller-Buschbaum, P. Structure and Charge Carrier Dynamics in Colloidal PbS Quantum Dot Solids. *J. Phys. Chem. Lett.* **2019**, *10*, 2058–2065.

(750) Chen, J.; Ye, X.; Murray, C. B. Systematic Electron Crystallographic Studies of Self-Assembled Binary Nanocrystal Superlattices. *ACS Nano* **2010**, *4*, 2374–2381.

(751) Jurow, M. J.; Morgenstern, T.; Eisler, C.; Kang, J.; Penzo, E.; Do, M.; Engelmayr, M.; Osowiecki, W. T.; Bekenstein, Y.; Tassone, C.; Wang, L. W.; Alivisatos, A. P.; Brutting, W.; Liu, Y. Manipulating the Transition Dipole Moment of CsPbBr₃ Perovskite Nanocrystals for Superior Optical Properties. *Nano Lett.* **2019**, *19*, 2489–2496.

(752) Li, B.; Binks, D.; Cao, G.; Tian, J. Engineering Halide Perovskite Crystals through Precursor Chemistry. *Small* **2019**, *15*, 1903613.

(753) Pratap, S.; Keller, E.; Müller-Buschbaum, P. Emergence of Lead Halide Perovskite Colloidal Dispersions through Aggregation and Fragmentation: Insights from the Nanoscale to the Mesoscale. *Nanoscale* **2019**, *11*, 3495–3499.

(754) Ban, M.; Zou, Y.; Rivett, J. P. H.; Yang, Y.; Thomas, T. H.; Tan, Y.; Song, T.; Gao, X.; Credgington, D.; Deschler, F.; Sirringhaus, H.; Sun, B. Solution-Processed Perovskite Light Emitting Diodes with Efficiency Exceeding 15% through Additive-Controlled Nanostructure Tailoring. *Nat. Commun.* **2018**, *9*, 3892.

(755) Davis, N. J.; de la Pena, F. J.; Tabachnyk, M.; Richter, J. M.; Lamboll, R. D.; Booker, E. P.; Wisnivesky Rocca Rivarola, F.; Griffiths, J. T.; Ducati, C.; Menke, S. M.; Deschler, F.; Greenham, N. C. Photon Reabsorption in Mixed CsPbCl₃:CsPbI₃ Perovskite Nanocrystal Films for Light-Emitting Diodes. *J. Phys. Chem. C* **2017**, *121*, 3790–3796.

(756) Pospelov, G.; Van Herck, W.; Burle, J.; Carmona Loaiza, J. M.; Durniak, C.; Fisher, J. M.; Ganeva, M.; Yurov, D.; Wuttke, J. BornAgain: Software for Simulating and Fitting Grazing-Incidence Small-Angle Scattering. *J. Appl. Crystallogr.* **2020**, *53*, 262–276.

(757) Jiang, Z. GIXSGUI: A MATLAB Toolbox for Grazing-Incidence X-Ray Scattering Data Visualization and Reduction, and Indexing of Buried Three-Dimensional Periodic Nanostructured Films. *J. Appl. Crystallogr.* **2015**, *48*, 917–926.

(758) Benecke, G.; Wagermaier, W.; Li, C.; Schwartzkopf, M.; Flucke, G.; Hoerth, R.; Zizak, I.; Burghammer, M.; Metwalli, E.; Müller-Buschbaum, P.; Trebbin, M.; Forster, S.; Paris, O.; Roth, S. V.; Fratzl, P. A Customizable Software for Fast Reduction and Analysis of Large X-Ray Scattering Data Sets: Applications of the New DPDA Package to Small-Angle X-Ray Scattering and Grazing-Incidence Small-Angle X-Ray Scattering. *J. Appl. Crystallogr.* **2014**, *47*, 1797–1803.

(759) Hammersley, A. P. FIT2D: A Multi-Purpose Data Reduction, Analysis and Visualization Program. *J. Appl. Crystallogr.* **2016**, *49*, 646–652.

(760) Cannesson, D.; Shornikova, E. V.; Yakovlev, D. R.; Rogge, T.; Mitioglu, A. A.; Ballottin, M. V.; Christianen, P. C.; Lhuillier, E.; Bayer, M.; Biadala, L. Negatively Charged and Dark Excitons in CsPbBr₃ Perovskite Nanocrystals Revealed by High Magnetic Fields. *Nano Lett.* **2017**, *17*, 6177–6183.

(761) Rong, Y.; Hu, Y.; Mei, A.; Tan, H.; Saidaminov, M. I.; Seok, S. I.; McGehee, M. D.; Sargent, E. H.; Han, H. Challenges for Commercializing Perovskite Solar Cells. *Science* **2018**, *361*, eaat8235.

(762) Stranks, S. D.; Burlakov, V. M.; Leijtens, T.; Ball, J. M.; Goriely, A.; Snaith, H. J. Recombination Kinetics in Organic-Inorganic Perovskites: Excitons, Free Charge, and Subgap States. *Phys. Rev. Appl.* **2014**, *2*, 034007.

(763) Walsh, A.; Zunger, A. Instilling Defect Tolerance in New Compounds. *Nat. Mater.* **2017**, *16*, 964–967.

(764) Rosales, B. A.; Mundt, L. E.; Allen, T. G.; Moore, D. T.; Prince, K. J.; Wolden, C. A.; Rumbles, G.; Schelhas, L. T.; Wheeler, L. M. Reversible Multicolor Chromism in Layered Formamidinium Metal Halide Perovskites. *Nat. Commun.* **2020**, *11*, 5234.

(765) Noh, J. H.; Im, S. H.; Heo, J. H.; Mandal, T. N.; Seok, S. I. Chemical Management for Colorful, Efficient, and Stable Inorganic–Organic Hybrid Nanostructured Solar Cells. *Nano Lett.* **2013**, *13*, 1764–1769.

(766) Eperon, G. E.; Stranks, S. D.; Menelaou, C.; Johnston, M. B.; Herz, L. M.; Snaith, H. J. Formamidinium Lead Trihalide: A Broadly Tunable Perovskite for Efficient Planar Heterojunction Solar Cells. *Energy Environ. Sci.* **2014**, *7*, 982–988.

(767) Sadhanala, A.; Deschler, F.; Thomas, T. H.; Dutton, S. E.; Goedel, K. C.; Hanusch, F. C.; Lai, M. L.; Steiner, U.; Bein, T.; Docampo, P.; Cahen, D.; Friend, R. H. Preparation of Single-Phase Films of CH₃NH₃Pb (I_{1-x}Br_x)₃ with Sharp Optical Band Edges. *J. Phys. Chem. Lett.* **2014**, *5*, 2501–2505.

(768) Kumawat, N. K.; Dey, A.; Kumar, A.; Gopinathan, S. P.; Narasimhan, K. L.; Kabra, D. Band Gap Tuning of CH₃NH₃Pb(Br_{1-x}Cl_x)₃ Hybrid Perovskite for Blue Electroluminescence. *ACS Appl. Mater. Interfaces* **2015**, *7*, 13119–13124.

(769) Coduri, M.; Strobel, T. A.; Szafrański, M.; Katrusiak, A.; Mahata, A.; Cova, F.; Bonomi, S.; Mosconi, E.; De Angelis, F.; Malavasi, L. Band Gap Engineering in MASnBr₃ and CsSnBr₃ Perovskites: Mechanistic Insights through the Application of Pressure. *J. Phys. Chem. Lett.* **2019**, *10*, 7398–7405.

(770) Umebayashi, T.; Asai, K.; Kondo, T.; Nakao, A. Electronic Structures of Lead Iodide Based Low-Dimensional Crystals. *Phys. Rev. B: Condens. Matter Mater. Phys.* **2003**, *67*, 155405.

(771) Butler, K. T.; Frost, J. M.; Walsh, A. Band Alignment of the Hybrid Halide Perovskites CH₃NH₃PbCl₃, CH₃NH₃PbBr₃ and CH₃NH₃PbI₃. *Mater. Horiz.* **2015**, *2*, 228–231.

(772) Payne, D. J.; Egdell, R. G.; Walsh, A.; Watson, G. W.; Guo, J.; Glans, P. A.; Learmonth, T.; Smith, K. E. Electronic Origins of Structural Distortions in Post-Transition Metal Oxides: Experimental and Theoretical Evidence for a Revision of the Lone Pair Model. *Phys. Rev. Lett.* **2006**, *96*, 157403.

(773) Brivio, F.; Butler, K. T.; Walsh, A.; Van Schilfgaarde, M. Relativistic Quasiparticle Self-Consistent Electronic Structure of Hybrid Halide Perovskite Photovoltaic Absorbers. *Phys. Rev. B: Condens. Matter Mater. Phys.* **2014**, *89*, 155204.

(774) Even, J.; Pedesseau, L.; Jancu, J.-M.; Katan, C. Importance of Spin–Orbit Coupling in Hybrid Organic/Inorganic Perovskites for Photovoltaic Applications. *J. Phys. Chem. Lett.* **2013**, *4*, 2999–3005.

(775) Filip, M. R.; Eperon, G. E.; Snaith, H. J.; Giustino, F. Steric Engineering of Metal-Halide Perovskites with Tunable Optical Band Gaps. *Nat. Commun.* **2014**, *5*, 5757.

(776) Brivio, F.; Walker, A. B.; Walsh, A. Structural and Electronic Properties of Hybrid Perovskites for High-Efficiency Thin-Film Photovoltaics from First-Principles. *APL Mater.* **2013**, *1*, 042111.

(777) Borriello, I.; Cantele, G.; Ninno, D. *Ab Initio* Investigation of Hybrid Organic-Inorganic Perovskites Based on Tin Halides. *Phys. Rev. B: Condens. Matter Mater. Phys.* **2008**, *77*, 235214.

(778) Meng, W.; Wang, X.; Xiao, Z.; Wang, J.; Mitzi, D. B.; Yan, Y. Parity-Forbidden Transitions and Their Impact on the Optical Absorption Properties of Lead-Free Metal Halide Perovskites and Double Perovskites. *J. Phys. Chem. Lett.* **2017**, *8*, 2999–3007.

(779) Dey, A.; Richter, A. F.; Debnath, T.; Huang, H.; Polavarapu, L.; Feldmann, J. Transfer of Direct to Indirect Bound Excitons by Electron Intervalley Scattering in $\text{Cs}_2\text{AgBiBr}_6$ Double Perovskite Nanocrystals. *ACS Nano* **2020**, *14*, 5855–5861.

(780) Saba, M.; Cadelano, M.; Marongiu, D.; Chen, F.; Sarritzu, V.; Sestu, N.; Figus, C.; Aresti, M.; Piras, R.; Geddo Lehmann, A.; Cannas, C.; Musinu, A.; Quochi, F.; Mura, A.; Bongiovanni, G. Correlated Electron–Hole Plasma in Organometal Perovskites. *Nat. Commun.* **2014**, *5*, 5049.

(781) Palummo, M.; Berrios, E.; Varsano, D.; Giorgi, G. Optical Excitations of Lead-Free Double Perovskites by *ab Initio* Excited-State Methods. *ACS Energy Lett.* **2020**, *5*, 457–463.

(782) De, A.; Das, S.; Mondal, N.; Samanta, A. Highly Luminescent Violet- and Blue-Emitting Stable Perovskite Nanocrystals. *ACS Mater. Lett.* **2019**, *1*, 116–122.

(783) Das, S.; De, A.; Samanta, A. Ambient Condition Mg^{2+} -Doping Producing Highly Luminescent Green- and Violet-Emitting Perovskite Nanocrystals with Reduced Toxicity and Enhanced Stability. *J. Phys. Chem. Lett.* **2020**, *11*, 1178–1188.

(784) Droseros, N.; Longo, G.; Brauer, J. C.; Sessolo, M.; Bolink, H. J.; Banerji, N. Origin of the Enhanced Photoluminescence Quantum Yield in MAPbBr_3 Perovskite with Reduced Crystal Size. *ACS Energy Lett.* **2018**, *3*, 1458–1466.

(785) Brennan, M. C.; Herr, J. E.; Nguyen-Beck, T. S.; Zinna, J.; Draguta, S.; Rouvimon, S.; Parkhill, J.; Kuno, M. Origin of the Size-Dependent Stokes Shift in CsPbBr_3 Perovskite Nanocrystals. *J. Am. Chem. Soc.* **2017**, *139*, 12201–12208.

(786) Blancon, J.-C.; Tsai, H.; Nie, W.; Stoumpos, C. C.; Pedesseau, L.; Katan, C.; Kepenekian, M.; Soe, C. M. M.; Appavoo, K.; Sfeir, M. Y.; Tretiak, S.; Ajayan, P. M.; Kanatzidis, M. G.; Even, J.; Crochet, J. J.; Mohite, A. D. Extremely Efficient Internal Exciton Dissociation through Edge States in Layered 2D Perovskites. *Science* **2017**, *355*, 1288–1292.

(787) Efros, A. L. Excitons in Quantum-Well Structures. *Sov. Phys. Semicond-USSR* **1986**, *20*, 808–812.

(788) Tanaka, K.; Takahashi, T.; Kondo, T.; Umebayashi, T.; Asai, K.; Ema, K. Image Charge Effect on Two-Dimensional Excitons in an Inorganic-Organic Quantum-Well Crystal. *Phys. Rev. B: Condens. Matter Mater. Phys.* **2005**, *71*, 045312.

(789) Saporì, D.; Kepenekian, M.; Pedesseau, L.; Katan, C.; Even, J. Quantum Confinement and Dielectric Profiles of Colloidal Nanoplatelets of Halide Inorganic and Hybrid Organic–Inorganic Perovskites. *Nanoscale* **2016**, *8*, 6369–6378.

(790) Katan, C.; Mercier, N.; Even, J. Quantum and Dielectric Confinement Effects in Lower-Dimensional Hybrid Perovskite Semiconductors. *Chem. Rev.* **2019**, *119*, 3140–3192.

(791) Chakraborty, R.; Nag, A. Correlation of Dielectric Confinement and Excitonic Binding Energy in 2D Layered Hybrid Perovskites Using Temperature Dependent Photoluminescence. *J. Phys. Chem. C* **2020**, *124*, 16177–16185.

(792) Takagi, H.; Kunugita, H.; Ema, K. Influence of the Image Charge Effect on Excitonic Energy Structure in Organic-Inorganic Multiple Quantum Well Crystals. *Phys. Rev. B: Condens. Matter Mater. Phys.* **2013**, *87*, 125421.

(793) Bohn, B. J.; Simon, T.; Gramlich, M.; Richter, A. F.; Polavarapu, L.; Urban, A. S.; Feldmann, J. Dephasing and Quantum Beating of Excitons in Methylammonium Lead Iodide Perovskite Nanoplatelets. *ACS Photonics* **2018**, *5*, 648–654.

(794) Singh, S.; Li, C.; Panzer, F.; Narasimhan, K.; Graeser, A.; Gujar, T. P.; Köhler, A.; Thelakkat, M.; Huetten, S.; Kabra, D. Effect of Thermal and Structural Disorder on the Electronic Structure of Hybrid Perovskite Semiconductor $\text{CH}_3\text{NH}_3\text{PbI}_3$. *J. Phys. Chem. Lett.* **2016**, *7*, 3014–3021.

(795) Wright, A. D.; Verdi, C.; Milot, R. L.; Eperon, G. E.; Pérez-Orsorio, M. A.; Snaith, H. J.; Giustino, F.; Johnston, M. B.; Herz, L. M. Electron-Phonon Coupling in Hybrid Lead Halide Perovskites. *Nat. Commun.* **2016**, *7*, 11755.

(796) Wehrenfennig, C.; Eperon, G. E.; Johnston, M. B.; Snaith, H. J.; Herz, L. M. High Charge Carrier Mobilities and Lifetimes in Organolead Trihalide Perovskites. *Adv. Mater.* **2014**, *26*, 1584–1589.

(797) Saxena, R.; Kangsabani, J.; Kumar, A.; Shahee, A.; Singh, S.; Jain, N.; Ghorui, S.; Kumar, V.; Mahajan, A. V.; Alam, A.; Kabra, D. Contrasting Temperature Dependence of the Band Gap in $\text{CH}_3\text{NH}_3\text{PbX}_3$ ($\text{X}=\text{I}$, Br , Cl): Insight from Lattice Dilatation and Electron-Phonon Coupling. *Phys. Rev. B: Condens. Matter Mater. Phys.* **2020**, *102*, 081201.

(798) Steele, J. A.; Puech, P.; Keshavarz, M.; Yang, R.; Banerjee, S.; Debroye, E.; Kim, C. W.; Yuan, H.; Heo, N. H.; Vanacken, J.; Walsh, A.; Hofkens, J.; Roeffaers, M. B. J. Giant Electron–Phonon Coupling and Deep Conduction Band Resonance in Metal Halide Double Perovskite. *ACS Nano* **2018**, *12*, 8081–8090.

(799) Zelewski, S. J.; Urban, J. M.; Surrente, A.; Maude, D. K.; Kuc, A.; Schade, L.; Johnson, R. D.; Dollmann, M.; Nayak, P. K.; Snaith, H. J.; Radaelli, P.; Kudrawiec, R.; Nicholas, R. J.; Plochocka, P.; Baranowski, M. Revealing the Nature of Photoluminescence Emission in the Metal-Halide Double Perovskite $\text{Cs}_2\text{AgBiBr}_6$. *J. Mater. Chem. C* **2019**, *7*, 8350–8356.

(800) Benin, B. M.; Dirin, D. N.; Morad, V.; Wörle, M.; Yakunin, S.; Raino, G.; Nazarenko, O.; Fischer, M.; Infante, I.; Kovalenko, M. V. Highly Emissive Self-Trapped Excitons in Fully Inorganic Zero-Dimensional Tin Halides. *Angew. Chem., Int. Ed.* **2018**, *57*, 11329–11333.

(801) Guo, Y.; Yaffe, O.; Hull, T. D.; Owen, J. S.; Reichman, D. R.; Brus, L. E. Dynamic Emission Stokes Shift and Liquid-Like Dielectric Solvation of Band Edge Carriers in Lead-Halide Perovskites. *Nat. Commun.* **2019**, *10*, 1175.

(802) Knox, R. S. Theory of Excitons. *Solid State Physics*; Academic Press: New York, 1963; Vol. 5, p 207.

(803) Kusrayev, Y. G.; Zakharchenya, B.; Karczewski, G.; Wojtowicz, T.; Kossut, J. Fine Structure of Exciton Levels in CdTeCdMgTe Quantum Wells. *Solid State Commun.* **1997**, *104*, 465–468.

(804) Chamarro, M.; Gourdon, C.; Lavallard, P.; Lublinskaya, O.; Ekimov, A. Enhancement of Electron–Hole Exchange Interaction in CdSe Nanocrystals: A Quantum Confinement Effect. *Phys. Rev. B: Condens. Matter Mater. Phys.* **1996**, *53*, 1336.

(805) Bayer, M.; Ortner, G.; Stern, O.; Kuther, A.; Gorbunov, A. A.; Forchel, A.; Hawrylak, P.; Fafard, S.; Hinzer, K.; Reinecke, T. L.; Walck, S. N.; Reithmaier, J. P.; Klopf, F.; Schafer, F. Fine Structure of Neutral and Charged Excitons in Self-Assembled $\text{In}(\text{Ga})\text{As}/(\text{Al})\text{GaAs}$ Quantum Dots. *Phys. Rev. B: Condens. Matter Mater. Phys.* **2002**, *65*, 195315.

(806) Sercel, P. C.; Lyons, J. L.; Wickramaratne, D.; Vaxenburg, R.; Bernstein, N.; Efros, A. L. Exciton Fine Structure in Perovskite Nanocrystals. *Nano Lett.* **2019**, *19*, 4068–4077.

(807) Efros, A. L.; Rosen, M.; Kuno, M.; Nirmal, M.; Norris, D. J.; Bawendi, M. Band-Edge Exciton in Quantum Dots of Semiconductors with a Degenerate Valence Band: Dark and Bright Exciton States. *Phys. Rev. B: Condens. Matter Mater. Phys.* **1996**, *54*, 4843.

(808) Korkusinski, M.; Vozny, O.; Hawrylak, P. Fine Structure and Size Dependence of Exciton and Biexciton Optical Spectra in CdSe Nanocrystals. *Phys. Rev. B: Condens. Matter Mater. Phys.* **2010**, *82*, 245304.

(809) Korkusinski, M.; Hawrylak, P. Atomistic Theory of Emission from Dark Excitons in Self-Assembled Quantum Dots. *Phys. Rev. B: Condens. Matter Mater. Phys.* **2013**, *87*, 115310.

(810) Smolenski, T.; Kazimierczuk, T.; Goryca, M.; Jakubczyk, T.; Kłopotowski, Ł.; Cywinski, Ł.; Wojnar, P.; Golnik, A.; Kossacki, P. In-Plane Radiative Recombination Channel of a Dark Exciton in Self-Assembled Quantum Dots. *Phys. Rev. B: Condens. Matter Mater. Phys.* **2012**, *86*, 241305.

(811) Nirmal, M.; Norris, D. J.; Kuno, M.; Bawendi, M. G.; Efros, A. L.; Rosen, M. Observation of the “Dark Exciton” in CdSe Quantum Dots. *Phys. Rev. Lett.* **1995**, *75*, 3728.

(812) Biadala, L.; Liu, F.; Tessier, M. D.; Yakovlev, D. R.; Dubertret, B.; Bayer, M. Recombination Dynamics of Band Edge Excitons in Quasi-Two-Dimensional CdSe Nanoplatelets. *Nano Lett.* **2014**, *14*, 1134–1139.

(813) Biadala, L.; Siebers, B.; Beyazit, Y.; Tessier, M. L. D.; Dupont, D.; Hens, Z.; Yakovlev, D. R.; Bayer, M. Band-Edge Exciton Fine Structure and Recombination Dynamics in InP/ZnS Colloidal Nanocrystals. *ACS Nano* **2016**, *10*, 3356–3364.

(814) Dey, A.; Rathod, P.; Kabra, D. Role of Localized States in Photoluminescence Dynamics of High Optical Gain CsPbBr₃ Nanocrystals. *Adv. Opt. Mater.* **2018**, *6*, 1800109.

(815) Chen, L.; Li, B.; Zhang, C.; Huang, X.; Wang, X.; Xiao, M. Composition-Dependent Energy Splitting between Bright and Dark Excitons in Lead Halide Perovskite Nanocrystals. *Nano Lett.* **2018**, *18*, 2074–2080.

(816) Tamarat, P.; Bodnarchuk, M. I.; Trebbia, J.-B.; Erni, R.; Kovalenko, M. V.; Even, J.; Lounis, B. The Ground Exciton State of Formamidinium Lead Bromide Perovskite Nanocrystals Is a Singlet Dark State. *Nat. Mater.* **2019**, *18*, 717–724.

(817) Xu, K.; Vliem, J. F.; Meijerink, A. Long-Lived Dark Exciton Emission in Mn-Doped CsPbCl₃ Perovskite Nanocrystals. *J. Phys. Chem. C* **2019**, *123*, 979–984.

(818) Fu, M.; Tamarat, P.; Huang, H.; Even, J.; Rogach, A. L.; Lounis, B. Neutral and Charged Exciton Fine Structure in Single Lead Halide Perovskite Nanocrystals Revealed by Magneto-Optical Spectroscopy. *Nano Lett.* **2017**, *17*, 2895–2901.

(819) Yin, C.; Chen, L.; Song, N.; Lv, Y.; Hu, F.; Sun, C.; Yu, W. W.; Zhang, C.; Wang, X.; Zhang, Y.; Xiao, M. Bright-Exciton Fine-Structure Splittings in Single Perovskite Nanocrystals. *Phys. Rev. Lett.* **2017**, *119*, 026401.

(820) Bar-Ad, S.; Bar-Joseph, I. Exciton Spin Dynamics in GaAs Heterostructures. *Phys. Rev. Lett.* **1992**, *68*, 349–352.

(821) Strohmair, S.; Dey, A.; Tong, Y.; Polavarapu, L.; Bohn, B. J.; Feldmann, J. Spin Polarization Dynamics of Free Charge Carriers in CsPbI₃ Nanocrystals. *Nano Lett.* **2020**, *20*, 4724–4730.

(822) Modern Problems in Condensed Matter Sciences. In *Optical Orientation*; Meier, F., Zakharchenya, B. P., Eds.; North-Holland Physics Publishing (Elsevier Science Publishers B.V.): Amsterdam, The Netherlands, 1984; pp 73–105.

(823) Giovanni, D.; Ma, H.; Chua, J.; Grätzel, M.; Ramesh, R.; Mhaisalkar, S.; Mathews, N.; Sum, T. C. Highly Spin-Polarized Carrier Dynamics and Ultralarge Photoinduced Magnetization in CH₃NH₃PbI₃ Perovskite Thin Films. *Nano Lett.* **2015**, *15*, 1553–1558.

(824) Di Nuzzo, D.; Cui, L.; Greenfield, J. L.; Zhao, B.; Friend, R. H.; Meskers, S. C. J. Circularly Polarized Photoluminescence from Chiral Perovskite Thin Films at Room Temperature. *ACS Nano* **2020**, *14*, 7610–7616.

(825) Kim, Y.-H.; Zhai, Y.; Gaulding, E. A.; Haberreutinger, S. N.; Moot, T.; Rosales, B. A.; Lu, H.; Hazarika, A.; Brunecky, R.; Wheeler, L. M.; Berry, J. J.; Beard, M. C.; Luther, J. M. Strategies to Achieve High Circularly Polarized Luminescence from Colloidal Organic–Inorganic Hybrid Perovskite Nanocrystals. *ACS Nano* **2020**, *14*, 8816–8825.

(826) Ma, J.; Fang, C.; Chen, C.; Jin, L.; Wang, J.; Wang, S.; Tang, J.; Li, D. Chiral 2D Perovskites with a High Degree of Circularly Polarized Photoluminescence. *ACS Nano* **2019**, *13*, 3659–3665.

(827) Wang, J.; Fang, C.; Ma, J.; Wang, S.; Jin, L.; Li, W.; Li, D. Aqueous Synthesis of Low-Dimensional Lead Halide Perovskites for Room-Temperature Circularly Polarized Light Emission and Detection. *ACS Nano* **2019**, *13*, 9473–9481.

(828) Billing, D. G.; Lemmerer, A. Bis[(S)- β -Phenethylammonium] Tribromoplumbeate(II). *Acta Crystallogr., Sect. E: Struct. Rep. Online* **2003**, *59*, M381–M383.

(829) Georgieva, Z. N.; Bloom, B. P.; Ghosh, S.; Waldeck, D. H. Imprinting Chirality onto the Electronic States of Colloidal Perovskite Nanoplatelets. *Adv. Mater.* **2018**, *30*, 1800097.

(830) Shi, Y.; Duan, P.; Huo, S.; Li, Y.; Liu, M. Endowing Perovskite Nanocrystals with Circularly Polarized Luminescence. *Adv. Mater.* **2018**, *30*, 1705011.

(831) Zhao, B.; Gao, X.; Pan, K.; Deng, J. Chiral Helical Polymer/Perovskite Hybrid Nanofibers with Intense Circularly Polarized Luminescence. *ACS Nano* **2021**, *15*, 7463–7471.

(832) Wang, L.; Xue, Y.; Cui, M.; Huang, Y.; Xu, H.; Qin, C.; Yang, J.; Dai, H.; Yuan, M. A Chiral Reduced-Dimension Perovskite for an Efficient Flexible Circularly Polarized Light Photodetector. *Angew. Chem., Int. Ed.* **2020**, *59*, 6442–6450.

(833) Ren, H.; Wu, Y.; Wang, C.; Yan, Y. 2D Perovskite Nanosheets with Intrinsic Chirality. *J. Phys. Chem. Lett.* **2021**, *12*, 2676–2681.

(834) Chen, W.; Zhang, S.; Zhou, M.; Zhao, T.; Qin, X.; Liu, X.; Liu, M.; Duan, P. Two-Photon Absorption-Based Upconverted Circularly Polarized Luminescence Generated in Chiral Perovskite Nanocrystals. *J. Phys. Chem. Lett.* **2019**, *10*, 3290–3295.

(835) Dang, Y.; Liu, X.; Sun, Y.; Song, J.; Hu, W.; Tao, X. Bulk Chiral Halide Perovskite Single Crystals for Active Circular Dichroism and Circularly Polarized Luminescence. *J. Phys. Chem. Lett.* **2020**, *11*, 1689–1696.

(836) Ahn, J.; Ma, S.; Kim, J.-Y.; Kyhm, J.; Yang, W.; Lim, J. A.; Kotov, N. A.; Moon, J. Chiral 2D Organic Inorganic Hybrid Perovskite with Circular Dichroism Tunable over Wide Wavelength Range. *J. Am. Chem. Soc.* **2020**, *142*, 4206–4212.

(837) Ahn, J.; Lee, E.; Tan, J.; Yang, W.; Kim, B.; Moon, J. A New Class of Chiral Semiconductors: Chiral-Organic-Molecule-Incorporating Organic–Inorganic Hybrid Perovskites. *Mater. Horiz.* **2017**, *4*, 851–856.

(838) Yuan, C.; Li, X.; Semin, S.; Feng, Y.; Rasing, T.; Xu, J. Chiral Lead Halide Perovskite Nanowires for Second-Order Nonlinear Optics. *Nano Lett.* **2018**, *18*, 5411–5417.

(839) Chen, C.; Gao, L.; Gao, W.; Ge, C.; Du, X.; Li, Z.; Yang, Y.; Niu, G.; Tang, J. Circularly Polarized Light Detection Using Chiral Hybrid Perovskite. *Nat. Commun.* **2019**, *10*, 1927.

(840) Long, G.; Sabatini, R.; Saidaminov, M. I.; Lakhwani, G.; Rasmussen, A.; Liu, X.; Sargent, E. H.; Gao, W. Chiral-Perovskite Optoelectronics. *Nat. Rev. Mater.* **2020**, *5*, 423–439.

(841) Cahn, R. S.; Ingold, C.; Prelog, V. Specification of Molecular Chirality. *Angew. Chem., Int. Ed. Engl.* **1966**, *5*, 385–415.

(842) Gal, J. Molecular Chirality in Chemistry and Biology: Historical Milestones. *Helv. Chim. Acta* **2013**, *96*, 1617–1657.

(843) Schreiber, R.; Luong, N.; Fan, Z.; Kuzyk, A.; Nickels, P. C.; Zhang, T.; Smith, D. M.; Yurke, B.; Kuang, W.; Gavorov, A. O.; Liedl, T. Chiral Plasmonic DNA Nanostructures with Switchable Circular Dichroism. *Nat. Commun.* **2013**, *4*, 2948.

(844) Zhou, C.; Duan, X.; Liu, N. DNA-Nanotechnology-Enabled Chiral Plasmonics: From Static to Dynamic. *Acc. Chem. Res.* **2017**, *50*, 2906–2914.

(845) Shen, X.; Song, C.; Wang, J.; Shi, D.; Wang, Z.; Liu, N.; Ding, B. Rolling up Gold Nanoparticle-Dressed DNA Origami into Three-Dimensional Plasmonic Chiral Nanostructures. *J. Am. Chem. Soc.* **2012**, *134*, 146–149.

(846) Herz, L. M. Charge-Carrier Dynamics in Organic-Inorganic Metal Halide Perovskites. *Annu. Rev. Phys. Chem.* **2016**, *67*, 65–89.

(847) Herz, L. M. Charge-Carrier Mobilities in Metal Halide Perovskites: Fundamental Mechanisms and Limits. *ACS Energy Lett.* **2017**, *2*, 1539–1548.

(848) Yang, Y.; Ostrowski, D. P.; France, R. M.; Zhu, K.; van de Lagemaat, J.; Luther, J. M.; Beard, M. C. Observation of a Hot-Phonon Bottleneck in Lead-Iodide Perovskites. *Nat. Photonics* **2016**, *10*, 53–59.

(849) Manser, J. S.; Kamat, P. V. Band Filling with Free Charge Carriers in Organometal Halide Perovskites. *Nat. Photonics* **2014**, *8*, 737–743.

(850) Li, M.; Bhaumik, S.; Goh, T. W.; Kumar, M. S.; Yantara, N.; Gratzel, M.; Mhaisalkar, S.; Mathews, N.; Sum, T. C. Slow Cooling

and Highly Efficient Extraction of Hot Carriers in Colloidal Perovskite Nanocrystals. *Nat. Commun.* **2017**, *8*, 14350.

(851) Mondal, N.; Samanta, A. Complete Ultrafast Charge Carrier Dynamics in Photo-Excited All-Inorganic Perovskite Nanocrystals (CsPbX_3). *Nanoscale* **2017**, *9*, 1878–1885.

(852) Chung, H.; Jung, S. I.; Kim, H. J.; Cha, W.; Sim, E.; Kim, D.; Koh, W.-K.; Kim, J. Composition-Dependent Hot Carrier Relaxation Dynamics in Cesium Lead Halide (CsPbX_3 , X = Br and I) Perovskite Nanocrystals. *Angew. Chem., Int. Ed.* **2017**, *56*, 4160–4164.

(853) Miyata, K.; Meggiolaro, D.; Trinh, M. T.; Joshi, P. P.; Mosconi, E.; Jones, S. C.; De Angelis, F.; Zhu, X.-Y. Large Polarons in Lead Halide Perovskites. *Sci. Adv.* **2017**, *3*, e1701217.

(854) Makarov, N. S.; Guo, S.; Isaienko, O.; Liu, W.; Robel, I. N.; Klimov, V. I. Spectral and Dynamical Properties of Single Excitons, Biexcitons, and Triions in Cesium–Lead-Halide Perovskite Quantum Dots. *Nano Lett.* **2016**, *16*, 2349–2362.

(855) Aneesh, J.; Swarnkar, A.; Kumar Ravi, V.; Sharma, R.; Nag, A.; Adarsh, K. V. Ultrafast Exciton Dynamics in Colloidal CsPbBr_3 Perovskite Nanocrystals: Biexciton Effect and Auger Recombination. *J. Phys. Chem. C* **2017**, *121*, 4734–4739.

(856) Rossi, D.; Wang, H.; Dong, Y.; Qiao, T.; Qian, X.; Son, D. H. Light-Induced Activation of Forbidden Exciton Transition in Strongly Confined Perovskite Quantum Dots. *ACS Nano* **2018**, *12*, 12436–12443.

(857) Hintermair, V. A.; Polavarapu, L.; Urban, A. S.; Feldmann, J. Accelerated Carrier Relaxation through Reduced Coulomb Screening in Two Dimensional Halide Perovskite Nanoplatelets. *ACS Nano* **2018**, *12*, 10151–10158.

(858) Diroll, B. T.; Schaller, R. D. Intraband Cooling in All-Inorganic and Hybrid Organic–Inorganic Perovskite Nanocrystals. *Adv. Funct. Mater.* **2019**, *29*, 1901725.

(859) Chen, J.; Messing, M. E.; Zheng, K.; Pullerits, T. Cation-Dependent Hot Carrier Cooling in Halide Perovskite Nanocrystals. *J. Am. Chem. Soc.* **2019**, *141*, 3532–3540.

(860) de Jong, E. M. L. D.; Yamashita, G.; Gomez, L.; Ashida, M.; Fujiwara, Y.; Gregorkiewicz, T. Multiexciton Lifetime in All-Inorganic CsPbBr_3 Perovskite Nanocrystals. *J. Phys. Chem. C* **2017**, *121*, 1941–1947.

(861) Hopper, T. R.; Gorodetsky, A.; Frost, J. M.; Müller, C.; Lovrincic, R.; Bakulin, A. A. Ultrafast Intraband Spectroscopy of Hot Carrier Cooling in Lead-Halide Perovskites. *ACS Energy Lett.* **2018**, *3*, 2199–2205.

(862) Madjet, M. E.; Berdiyorov, G. R.; El-Mellouhi, F.; Alharbi, F. H.; Akimov, A. V.; Kais, S. Cation Effect on Hot Carrier Cooling in Halide Perovskite Materials. *J. Phys. Chem. Lett.* **2017**, *8*, 4439–4445.

(863) Li, Y.; Ding, T.; Luo, X.; Tian, Y.; Lu, X.; Wu, K. Synthesis and Spectroscopy of Monodispersed, Quantum-Confining FAPbBr_3 Perovskite Nanocrystals. *Chem. Mater.* **2020**, *32*, 549–556.

(864) Verma, S. D.; Gu, Q.; Sadhanala, A.; Venugopalan, V.; Rao, A. Slow Carrier Cooling in Hybrid Pb–Sn Halide Perovskites. *ACS Energy Lett.* **2019**, *4*, 736–740.

(865) Fang, H.-H.; Adjokatse, S.; Shao, S.; Even, J.; Loi, M. A. Long-Lived Hot-Carrier Light Emission and Large Blue Shift in Formamidinium Tin Triiodide Perovskites. *Nat. Commun.* **2018**, *9*, 243.

(866) Li, M.; Fu, J.; Xu, Q.; Sum, T. C. Slow Hot-Carrier Cooling in Halide Perovskites: Prospects for Hot-Carrier Solar Cells. *Adv. Mater.* **2019**, *31*, 1802486.

(867) Li, Y.; Lai, R.; Luo, X.; Liu, X.; Ding, T.; Lu, X.; Wu, K. On the Absence of a Phonon Bottleneck in Strongly Confined CsPbBr_3 Perovskite Nanocrystals. *Chem. Sci.* **2019**, *10*, 5983–5989.

(868) Yin, J.; Maity, P.; Naphade, R.; Cheng, B.; He, J.-H.; Bakr, O. M.; Bredas, J.-L.; Mohammed, O. F. Tuning Hot Carrier Cooling Dynamics by Dielectric Confinement in Two-Dimensional Hybrid Perovskite Crystals. *ACS Nano* **2019**, *13*, 12621–12629.

(869) Kaur, G.; Justice Babu, K.; Ghorai, N.; Goswami, T.; Maiti, S.; Ghosh, H. N. Polaron-Mediated Slow Carrier Cooling in a Type-1 3D/0D $\text{CsPbBr}_3@\text{Cs}_4\text{PbBr}_6$ Core–Shell Perovskite System. *J. Phys. Chem. Lett.* **2019**, *10*, 5302–5311.

(870) Brandt, R. E.; Poindexter, J. R.; Gorai, P.; Kurchin, R. C.; Hoyer, R. L. Z.; Nienhaus, L.; Wilson, M. W. B.; Polizzetti, J. A.; Sereika, R.; Žaltauskas, R.; Lee, L. C.; Macmanus-Driscoll, J. L.; Bawendi, M.; Stevanovic, V.; Buonassisi, T. Searching for “Defect-Tolerant” Photovoltaic Materials: Combined Theoretical and Experimental Screening. *Chem. Mater.* **2017**, *29*, 4667–4674.

(871) Dequilette, D. W.; Frohma, K.; Emin, D.; Kirchartz, T.; Bulovic, V.; Ginger, D. S.; Stranks, S. D. Charge-Carrier Recombination in Halide Perovskites Focus Review. *Chem. Rev.* **2019**, *119*, 11007–11019.

(872) Mondal, N.; De, A.; Das, S.; Paul, S.; Samanta, A. Ultrafast Carrier Dynamics of Metal Halide Perovskite Nanocrystals and Perovskite-Composites. *Nanoscale* **2019**, *11*, 9796–9818.

(873) Zheng, X.; Hou, Y.; Sun, H.-T.; Mohammed, O. F.; Sargent, E. H.; Bakr, O. M. Reducing Defects in Halide Perovskite Nanocrystals for Light Emitting Applications. *J. Phys. Chem. Lett.* **2019**, *10*, 2629–2640.

(874) Ball, J. M.; Petrozza, A. Defects in Perovskite-Halides and Their Effects in Solar Cells. *Nat. Mater.* **2016**, *1*, 16149.

(875) Jin, H.; Debroye, E.; Keshavarz, M.; Scheblykin, I. G.; Roeffaers, M. B. J.; Hofkens, J.; Steele, J. A. It’s A Trap! On the Nature of Localised States and Charge Trapping in Lead Halide Perovskites. *Mater. Horiz.* **2020**, *7*, 397–410.

(876) Saxena, R.; Kumar, A.; Jain, N.; Kumawat, N. K.; Narasimhan, K. L.; Kabra, D. Photophysical Model for Non-Exponential Relaxation Dynamics in Hybrid Perovskite Semiconductors. *J. Phys. Chem. C* **2018**, *122*, 1119–1124.

(877) Chirvony, V. S.; Gonzalez-Carrero, S.; Suarez, I.; Galian, R. E.; Sessolo, M.; Bolink, H. J.; Martínez-Pastor, J. P.; Perez-Prieto, J. Delayed Luminescence in Lead Halide Perovskite Nanocrystals. *J. Phys. Chem. C* **2017**, *121*, 13381–13390.

(878) Wang, Y.; Zhi, M.; Chan, Y. Delayed Exciton Formation involving Energetically Shallow Trap States in Colloidal CsPbBr_3 Quantum Dots. *J. Phys. Chem. C* **2017**, *121*, 28498–28505.

(879) Liu, F.; Zhang, Y.; Ding, C.; Toyoda, T.; Ogomi, Y.; Ripolles, T. S.; Hayase, S.; Minemoto, T.; Yoshino, K.; Dai, S.; Shen, Q. Ultrafast Electron Injection from Photoexcited Perovskite CsPbI_3 QDs into TiO_2 Nanoparticles with Injection Efficiency near 99%. *J. Phys. Chem. Lett.* **2018**, *9*, 294–297.

(880) Rossi, D.; Parobek, D.; Dong, Y.; Son, D. H. Dynamics of Exciton–Mn Energy Transfer in Mn-Doped CsPbCl_3 Perovskite Nanocrystals. *J. Phys. Chem. C* **2017**, *121*, 17143–17149.

(881) Lai, R.; Wu, K. Picosecond Electron Trapping Limits the Emissivity of CsPbCl_3 Perovskite Nanocrystals. *J. Chem. Phys.* **2019**, *151*, 194701.

(882) Ahmed, T.; Seth, S.; Samanta, A. Mechanistic Investigation of the Defect Activity Contributing to the Photoluminescence Blinking of CsPbBr_3 Perovskite Nanocrystals. *ACS Nano* **2019**, *13*, 13537–13544.

(883) Mandal, S.; Mukherjee, S.; De, C. K.; Roy, D.; Ghosh, S.; Mandal, P. K. Extent of Shallow/Deep Trap States Beyond the Conduction Band Minimum in Defect-Tolerant CsPbBr_3 Perovskite Quantum Dot: Control over the Degree of Charge Carrier Recombination. *J. Phys. Chem. Lett.* **2020**, *11*, 1702–1707.

(884) Yang, B.; Mao, X.; Hong, F.; Meng, W.; Tang, Y.; Xia, X.; Yang, S.; Deng, W.; Han, K. Lead-Free Direct Band Gap Double-Perovskite Nanocrystals with Bright Dual-Color Emission. *J. Am. Chem. Soc.* **2018**, *140*, 17001–17006.

(885) Yang, B.; Han, K. Charge-Carrier Dynamics of Lead-Free Halide Perovskite Nanocrystals. *Acc. Chem. Res.* **2019**, *52*, 3188–3198.

(886) Woo, H. C.; Choi, J. W.; Shin, J.; Chin, S.-H.; Ann, M. H.; Lee, C.-L. Temperature-Dependent Photoluminescence of $\text{CH}_3\text{NH}_3\text{PbBr}_3$ Perovskite Quantum Dots and Bulk Counterparts. *J. Phys. Chem. Lett.* **2018**, *9*, 4066–4074.

(887) Makarov, N. S.; Guo, S.; Isaienko, O.; Liu, W.; Robel, I.; Klimov, V. I. Spectral and Dynamical Properties of Single Excitons, Biexcitons, and Triions in Cesium–Lead-Halide Perovskite Quantum Dots. *Nano Lett.* **2016**, *16*, 2349–2362.

(888) Eperon, G. E.; Jedlicka, E.; Ginger, D. S. Biexciton Auger Recombination Differs in Hybrid and Inorganic Halide Perovskite Quantum Dots. *J. Phys. Chem. Lett.* **2018**, *9*, 104–109.

(889) Klimov, V. I. Spectral and Dynamical Properties of Multie excitons in Semiconductor Nanocrystals. *Annu. Rev. Phys. Chem.* **2007**, *58*, 635–673.

(890) Egger, D. A.; Bera, A.; Cahen, D.; Hodes, G.; Kirchartz, T.; Kronik, L.; Lovrincic, R.; Rappe, A. M.; Reichman, D. R.; Yaffe, O. What Remains Unexplained about the Properties of Halide Perovskites? *Adv. Mater.* **2018**, *30*, 1800691.

(891) Chen, J.; Zhang, Q.; Shi, J.; Zhang, S.; Du, W.; Mi, Y.; Shang, Q.; Liu, P.; Sui, X.; Wu, X.; Wang, R.; Peng, B.; Zhong, H.; Xing, G.; Qiu, X.; Sum, T. C.; Liu, X. Room Temperature Continuous-Wave Excited Biexciton Emission in Perovskite Nanoplatelets via Plasmonic Nonlinear Fano Resonance. *Commun. Phys.* **2019**, *2*, 80.

(892) Straus, D. B.; Kagan, C. R. Electrons, Excitons, and Phonons in Two-Dimensional Hybrid Perovskites: Connecting Structural, Optical, and Electronic Properties. *J. Phys. Chem. Lett.* **2018**, *9*, 1434–1447.

(893) Jiang, Y.; Wang, X.; Pan, A. Properties of Excitons and Photogenerated Charge Carriers in Metal Halide Perovskites. *Adv. Mater.* **2019**, *31*, 1806671.

(894) Miyata, A.; Mitioglu, A.; Plochocka, P.; Portugall, O.; Wang, J. T.-W.; Stranks, S. D.; Snaith, H. J.; Nicholas, R. J. Direct Measurement of the Exciton Binding Energy and Effective Masses for Charge Carriers in Organic–Inorganic Tri-Halide Perovskites. *Nat. Phys.* **2015**, *11*, 582–587.

(895) Kumagai, M.; Takagahara, T. Excitonic and Nonlinear-Optical Properties of Dielectric Quantum-Well Structures. *Phys. Rev. B: Condens. Matter Mater. Phys.* **1989**, *40*, 12359–12381.

(896) Yang, Y.; Yang, M.; Li, Z.; Crisp, R.; Zhu, K.; Beard, M. C. Comparison of Recombination Dynamics in $\text{CH}_3\text{NH}_3\text{PbBr}_3$ and $\text{CH}_3\text{NH}_3\text{PbI}_3$ Perovskite Films: Influence of Exciton Binding Energy. *J. Phys. Chem. Lett.* **2015**, *6*, 4688–4692.

(897) Hong, X.; Ishihara, T.; Nurmiikko, A. V. Dielectric Confinement Effect on Excitons in PbI_4 -Based Layered Semiconductors. *Phys. Rev. B: Condens. Matter Mater. Phys.* **1992**, *45*, 6961–6964.

(898) Li, J.; Luo, L.; Huang, H.; Ma, C.; Ye, Z.; Zeng, J.; He, H. 2D Behaviors of Excitons in Cesium Lead Halide Perovskite Nanoplatelets. *J. Phys. Chem. Lett.* **2017**, *8*, 1161–1168.

(899) Kumar, S.; Jagielski, J.; Yakunin, S.; Rice, P.; Chiu, Y. C.; Wang, M.; Nedelcu, G.; Kim, Y.; Lin, S.; Santos, E. J. G.; Kovalenko, M. V.; Shih, C. J. Efficient Blue Electroluminescence Using Quantum-Confining Two-Dimensional Perovskites. *ACS Nano* **2016**, *10*, 9720–9729.

(900) Kumar, S.; Jagielski, J.; Kallikounis, N.; Kim, Y.-H.; Wolf, C.; Jenny, F.; Tian, T.; Hofer, C. J.; Chiu, Y.-C.; Stark, W. J.; Lee, T.-W.; Shih, C.-J. Ultrapure Green Light-Emitting Diodes Using Two-Dimensional Formamidinium Perovskites: Achieving Recommendation 2020 Color Coordinates. *Nano Lett.* **2017**, *17*, 5277–5284.

(901) Blancon, J. C.; Stier, A. V.; Tsai, H.; Nie, W.; Stoumpos, C. C.; TraorE, B.; Pedesseau, L.; Kepenekian, M.; Katsutani, F.; Noe, G. T.; Kono, J.; Tretiak, S.; Crooker, S. A.; Katan, C.; Kanatzidis, M. G.; Crochet, J. J.; Even, J.; Mohite, A. D. Scaling Law for Excitons in 2D Perovskite Quantum Wells. *Nat. Commun.* **2018**, *9*, 2254.

(902) Zhai, Y.; Baniya, S.; Zhang, C.; Li, J.; Haney, P.; Sheng, C.-X.; Ehrenfreund, E.; Vardeny, Z. V. Giant Rashba Splitting in 2D Organic-Inorganic Halide Perovskites Measured by Transient Spectroscopies. *Sci. Adv.* **2017**, *3*, e1700704.

(903) Schaller, R. D.; Sykora, M.; Pietryga, J. M.; Klimov, V. I. Seven Excitons at A Cost of One: Redefining the Limits for Conversion Efficiency of Photons into Charge Carriers. *Nano Lett.* **2006**, *6*, 424–429.

(904) Castañeda, J. A.; Nagamine, G.; Yassitepe, E.; Bonato, L. G.; Voznyy, O.; Hoogland, S.; Nogueira, A. F.; Sargent, E. H.; Cruz, C. H. B.; Padilha, L. A. Efficient Biexciton Interaction in Perovskite Quantum Dots under Weak and Strong Confinement. *ACS Nano* **2016**, *10*, 8603–8609.

(905) Soetan, N.; Puretzky, A.; Reid, K.; Boulesbaa, A.; Zarick, H. F.; Hunt, A.; Rose, O.; Rosenthal, S.; Geohegan, D. B.; Bardhan, R. Ultrafast Spectral Dynamics of $\text{CsPb}(\text{Br}_{x}\text{Cl}_{1-x})_3$ Mixed-Halide Nanocrystals. *ACS Photonics* **2018**, *5*, 3575–3583.

(906) Mondal, A.; Aneesh, J.; Kumar Ravi, V.; Sharma, R.; Mir, W. J.; Beard, M. C.; Nag, A.; Adarsh, K. V. Ultrafast Exciton Many-Body Interactions and Hot-Phonon Bottleneck in Colloidal Cesium Lead Halide Perovskite Nanocrystals. *Phys. Rev. B: Condens. Matter Mater. Phys.* **2018**, *98*, 115418.

(907) Li, Y.; Ding, T.; Luo, X.; Chen, Z.; Liu, X.; Lu, X.; Wu, K. Biexciton Auger Recombination in Mono-Dispersed, Qntum-Confining CsPbBr_3 Povskite Nanocrystals Obeys Universal Volume-Scaling. *Nano Res.* **2019**, *12*, 619–623.

(908) Manzi, A.; Tong, Y.; Feucht, J.; Yao, E.-P.; Polavarapu, L.; Urban, A. S.; Feldmann, J. Resonantly Enhanced Multiple Exciton Generation through Below-Band-Gap Multi-Photon Absorption in Perovskite Nanocrystals. *Nat. Commun.* **2018**, *9*, 1518.

(909) Li, M.; Begum, R.; Fu, J.; Xu, Q.; Koh, T. M.; Veldhuis, S. A.; Grätzel, M.; Mathews, N.; Mhaisalkar, S.; Sum, T. C. Low Threshold and Efficient Multiple Exciton Generation in Halide Perovskite Nanocrystals. *Nat. Commun.* **2018**, *9*, 4197.

(910) de Weerd, C.; Gomez, L.; Capretti, A.; Lebrun, D. M.; Matsubara, E.; Lin, J.; Ashida, M.; Spoor, F. C. M.; Siebbeles, L. D. A.; Houtepen, A. J.; Suenaga, K.; Fujiwara, Y.; Gregorkiewicz, T. Efficient Carrier Multiplication in CsPbI_3 Perovskite Nanocrystals. *Nat. Commun.* **2018**, *9*, 4199.

(911) Ahumada-Lazo, R.; Alanis, J. A.; Parkinson, P.; Binks, D. J.; Hardman, S. J. O.; Griffiths, J. T.; Wisnivesky Rocca Rivarola, F.; Humphrey, C. J.; Ducati, C.; Davis, N. J. L. K. Emission Properties and Ultrafast Carrier Dynamics of CsPbCl_3 Perovskite Nanocrystals. *J. Phys. Chem. C* **2019**, *123*, 2651–2657.

(912) Mondal, N.; De, A.; Samanta, A. Biexciton Generation and Dissociation Dynamics in Formamidiniumand Chloride-Doped Cesium Lead Iodide Perovskite Nanocrystals. *J. Phys. Chem. Lett.* **2018**, *9*, 3673–3679.

(913) Li, Q.; Yang, Y.; Que, W.; Lian, T. Size- and Morphology-Dependent Auger Recombination in CsPbBr_3 Perovskite Two-Dimensional Nanoplatelets and One-Dimensional Nanorods. *Nano Lett.* **2019**, *19*, 5620–5627.

(914) Seth, S.; Ahmed, T.; Samanta, A. Photoluminescence Flickering and Blinking of Single CsPbBr_3 Perovskite Nanocrystals: Revealing Explicit Carrier Recombination Dynamics. *J. Phys. Chem. Lett.* **2018**, *9*, 7007–7014.

(915) Yarita, N.; Tahara, H.; Saruyama, M.; Kawakami, T.; Sato, R.; Teranishi, T.; Kanemitsu, Y. Impact of Postsynthetic Surface Modification on Photoluminescence Intermittency in Formamidinium Lead Bromide Perovskite Nanocrystals. *J. Phys. Chem. Lett.* **2017**, *8*, 6041–6047.

(916) Yarita, N.; Tahara, H.; Ihara, T.; Kawakami, T.; Sato, R.; Saruyama, M.; Teranishi, T.; Kanemitsu, Y. Dynamics of Charged Excitons and Biexcitons in CsPbBr_3 Perovskite Nanocrystals Revealed by Femtosecond Transient-Absorption and Single-Dot Luminescence Spectroscopy. *J. Phys. Chem. Lett.* **2017**, *8*, 1413–1418.

(917) Wang, J.; Ding, T.; Leng, J.; Jin, S.; Wu, K. Intact"Carrier Doping by Pump–Pump–Probe Spectroscopy in Combination with Interfacial Charge Transfer: A Case Study of CsPbBr_3 Nanocrystals. *J. Phys. Chem. Lett.* **2018**, *9*, 3372–3377.

(918) Yarita, N.; Aharen, T.; Tahara, H.; Saruyama, M.; Kawakami, T.; Sato, R.; Teranishi, T.; Kanemitsu, Y. Observation of Positive and Negative Trions in Organic-Inorganic Hybrid Perovskite Nanocrystals. *Phys. Rev. Mater.* **2018**, *2*, 116003.

(919) Nakahara, S.; Tahara, H.; Yumoto, G.; Kawakami, T.; Saruyama, M.; Sato, R.; Teranishi, T.; Kanemitsu, Y. Suppression of Trion Formation in CsPbBr_3 Perovskite Nanocrystals by Postsynthetic Surface Modification. *J. Phys. Chem. C* **2018**, *122*, 22188–22193.

(920) Kanemitsu, Y. Trion Dynamics in Lead Halide Perovskite Nanocrystals. *J. Chem. Phys.* **2019**, *151*, 170902.

(921) Wu, K.; Liang, G.; Shang, Q.; Ren, Y.; Kong, D.; Lian, T. Ultrafast Interfacial Electron and Hole Transfer from CsPbBr_3 Perovskite Quantum Dots. *J. Am. Chem. Soc.* **2015**, *137*, 12792–12795.

(922) Nair, V. C.; Muthu, C.; Rogach, A. L.; Kohara, R.; Biju, V. Channeling Exciton Migration into Electron Transfer in Formamidinium Lead Bromide Perovskite Nanocrystal/Fullerene Composites. *Angew. Chem., Int. Ed.* **2017**, *56*, 1214–1218.

(923) Mandal, S.; George, L.; Tkachenko, N. V. Charge Transfer Dynamics in CsPbBr_3 Perovskite Quantum Dots–Anthraquinone/Fullerene (C60) Hybrids. *Nanoscale* **2019**, *11*, 862–869.

(924) Ahmed, G. H.; Liu, J.; Parida, M. R.; Murali, B.; Bose, R.; Alyami, N. M.; Hedhili, M. N.; Peng, W.; Pan, J.; Besong, T. M. D.; Bakr, O. M.; Mohammed, O. F. Shape-Tunable Charge Carrier Dynamics at the Interfaces Between Perovskite Nanocrystals and Molecular Acceptors. *J. Phys. Chem. Lett.* **2016**, *7*, 3913–3919.

(925) Zhang, Y.-X.; Wang, H.-Y.; Zhang, Z.-Y.; Zhang, Y.; Sun, C.; Yue, Y.-Y.; Wang, L.; Chen, Q.-D.; Sun, H.-B. Photoluminescence Quenching of Inorganic Cesium Lead Halides Perovskite Quantum Dots. *Phys. Chem. Chem. Phys.* **2017**, *19*, 1920–1926.

(926) Mandal, S.; Tkachenko, N. V. Multiphoton Excitation of CsPbBr_3 Perovskite Quantum Dots (Pqds): How Many Electrons Can One PQD Donate to Multiple Molecular Acceptors? *J. Phys. Chem. Lett.* **2019**, *10*, 2775–2781.

(927) De, A.; Mondal, N.; Samanta, A. Hole Transfer Dynamics from Photoexcited Cesium Lead Halide Perovskite Nanocrystals: 1-Aminopyrene as Hole Acceptor. *J. Phys. Chem. C* **2018**, *122*, 13617–13623.

(928) Dubose, J. T.; Kamat, P. V. Probing Perovskite Photocatalysis. Interfacial Electron Transfer Between CsPbBr_3 and Ferrocene Redox Couple. *J. Phys. Chem. Lett.* **2019**, *10*, 6074–6080.

(929) Lu, H.; Chen, X.; Anthony, J. E.; Johnson, J. C.; Beard, M. C. Sensitizing Singlet Fission With Perovskite Nanocrystals. *J. Am. Chem. Soc.* **2019**, *141*, 4919–4927.

(930) Maity, P.; Dana, J.; Ghosh, H. N. Multiple Charge Transfer Dynamics in Colloidal CsPbBr_3 Perovskite Quantum Dots Sensitized Molecular Adsorbate. *J. Phys. Chem. C* **2016**, *120*, 18348–18354.

(931) Begum, R.; Parida, M. R.; Abdelhady, A. L.; Murali, B.; Alyami, N. M.; Ahmed, G. H.; Hedhili, M. N.; Bakr, O. M.; Mohammed, O. F. Engineering Interfacial Charge Transfer in CsPbBr_3 Perovskite Nanocrystals by Heterovalent Doping. *J. Am. Chem. Soc.* **2017**, *139*, 731–737.

(932) Sarkar, S.; Ravi, V. K.; Banerjee, S.; Yettapu, G. R.; Markad, G. B.; Nag, A.; Mandal, P. Terahertz Spectroscopic Probe of Hot Electron and Hole Transfer from Colloidal CsPbBr_3 Perovskite Nanocrystals. *Nano Lett.* **2017**, *17*, 5402–5407.

(933) Shang, Q.; Kaledin, A. L.; Li, Q.; Lian, T. Size Dependent Charge Separation and Recombination in CsPbI_3 Perovskite Quantum Dots. *J. Chem. Phys.* **2019**, *151*, 074705.

(934) De, A.; Das, S.; Samanta, A. Hot Hole Transfer Dynamics from CsPbBr_3 Perovskite Nanocrystals. *ACS Energy Lett.* **2020**, *5*, 2246–2252.

(935) Luo, X.; Liang, G.; Wang, J.; Liu, X.; Wu, K. Picosecond Multi-Hole Transfer and Microsecond Charge-Separated States at the Perovskite Nanocrystal/Tetracene Interface. *Chem. Sci.* **2019**, *10*, 2459–2464.

(936) Scheidt, R. A.; Kerns, E.; Kamat, P. V. Interfacial Charge Transfer Between Excited CsPbBr_3 Nanocrystals and TiO_2 : Charge Injection Versus Photodegradation. *J. Phys. Chem. Lett.* **2018**, *9*, 5962–5969.

(937) Kobosko, S. M.; Dubose, J. T.; Kamat, P. V. Perovskite Photocatalysis. Methyl Viologen Induces Unusually Long-Lived Charge Carrier Separation in CsPbBr_3 Nanocrystals. *ACS Energy Lett.* **2020**, *5*, 221–223.

(938) Li, Q.; Lian, T. Ultrafast Charge Separation in Two-Dimensional CsPbBr_3 Perovskite Nanoplatelets. *J. Phys. Chem. Lett.* **2019**, *10*, 566–573.

(939) Dana, J.; Maity, P.; Jana, B.; Maiti, S.; Ghosh, H. N. Concurrent Ultrafast Electron- and Hole-Transfer Dynamics in CsPbBr_3 Perovskite and Quantum Dots. *ACS Omega* **2018**, *3*, 2706–2714.

(940) Brumberg, A.; Diroll, B. T.; Nedelcu, G.; Sykes, M. E.; Liu, Y.; Harvey, S. M.; Wasielewski, M. R.; Kovalenko, M. V.; Schaller, R. D. Material Dimensionality Effects on Electron Transfer Rates Between CsPbBr_3 and CdSe Nanoparticles. *Nano Lett.* **2018**, *18*, 4771–4776.

(941) Quintero-Bermudez, R.; Sabatini, R. P.; Lejay, M.; Voznyy, O.; Sargent, E. H. Small-Band-Offset Perovskite Shells Increase Auger Lifetime in Quantum Dot Solids. *ACS Nano* **2017**, *11*, 12378–12384.

(942) Galar, P.; Piatkowski, P.; Ngo, T. T.; Gutierrez, M.; Mora-Sero, I.; Douhal, A. Perovskite–Quantum Qots Interface: Deciphering Its Ultrafast Charge Carrier Dynamics. *Nano Energy* **2018**, *49*, 471–480.

(943) Mondal, N.; De, A.; Samanta, A. All-Inorganic Perovskite Nanocrystal Assisted Extraction of Hot Electrons and Biexcitons from Photoexcited Cdte Quantum Dots. *Nanoscale* **2018**, *10*, 639–645.

(944) Yao, E.-P.; Bohn, B. J.; Tong, Y.; Huang, H.; Polavarapu, L.; Feldmann, J. Exciton Diffusion Lengths and Dissociation Rates in CsPbBr_3 Nanocrystal–Fullerene Composites: Layer-by-Layer Versus Blend Structures. *Adv. Opt. Mater.* **2019**, *7*, 1801776.

(945) Vanorman, Z. A.; Bieber, A. S.; Wieghold, S.; Nienhaus, L. A. Perspective on Triplet Fusion Upconversion: Triplet Sensitizers Beyond Quantum Dots. *MRS Commun.* **2019**, *9*, 924–935.

(946) He, S.; Luo, X.; Liu, X.; Li, Y.; Wu, K. Visible-to-Ultraviolet Upconversion Efficiency above 10% Sensitized by Quantum-Confining Perovskite Nanocrystals. *J. Phys. Chem. Lett.* **2019**, *10*, 5036–5040.

(947) Mase, K.; Okumura, K.; Yanai, N.; Kimizuka, N. Triplet Sensitization by Perovskite Nanocrystals for Photon Upconversion. *Chem. Commun.* **2017**, *53*, 8261–8264.

(948) Okumura, K.; Yanai, N.; Kimizuka, N. Visible-to-UV Photon Upconversion Sensitized by Lead Halide Perovskite Nanocrystals. *Chem. Lett.* **2019**, *48*, 1347–1350.

(949) Nienhaus, L.; Correa-Baena, J.-P.; Wieghold, S.; Einzinger, M.; Lin, T.-A.; Shulenberger, K. E.; Klein, N. D.; Wu, M.; Bulović, V.; Buonassisi, T.; Baldo, M. A.; Bawendi, M. G. Triplet-Sensitization by Lead Halide Perovskite Thin Films for Near-Infrared-ToVisible Upconversion. *ACS Energy Lett.* **2019**, *4*, 888–895.

(950) Hu, H.; Meier, F.; Zhao, D.; Abe, Y.; Gao, Y.; Chen, B.; Salim, T.; Chia, E. E. M.; Qiao, X.; Deibel, C.; Lam, Y. M. Efficient Room-Temperature Phosphorescence from Organic-Inorganic Hybrid Perovskites by Molecular Engineering. *Adv. Mater.* **2018**, *30*, 1707621.

(951) Mondal, N.; De, A.; Seth, S.; Ahmed, T.; Das, S.; Paul, S.; Gautam, R. K.; Samanta, A. Dark Excitons of the Perovskites and Sensitization of Molecular Triplets. *ACS Energy Lett.* **2021**, *6*, 588–597.

(952) Luo, X.; Lai, R.; Li, Y.; Han, Y.; Liang, G.; Liu, X.; Ding, T.; Wang, J.; Wu, K. Triplet Energy Transfer from CsPbBr_3 Nanocrystals Enabled by Quantum Confinement. *J. Am. Chem. Soc.* **2019**, *141*, 4186–4190.

(953) Luo, X.; Han, Y.; Chen, Z.; Li, Y.; Liang, G.; Liu, X.; Ding, T.; Nie, C.; Wang, M.; Castellano, F. N.; Wu, K. Mechanisms of Triplet Energy Transfer Across the Inorganic Nanocrystal/Organic Molecule Interface. *Nat. Commun.* **2020**, *11*, 28.

(954) Matylitsky, V. V.; Dworak, L.; Breus, V. V.; Basche, T.; Wachtveitl, J. Ultrafast Charge Separation in Multiexcited CdSe Quantum Dots Mediated by Adsorbed Electron Acceptors. *J. Am. Chem. Soc.* **2009**, *131*, 2424–2425.

(955) Huang, J.; Huang, Z.; Yang, Y.; Zhu, H.; Lian, T. Multiple Exciton Dissociation in CdSe Quantum Dots by Ultrafast Electron Transfer to Adsorbed Methylene Blue. *J. Am. Chem. Soc.* **2010**, *132*, 4858–4864.

(956) Lim, S. S.; Giovanni, D.; Zhang, Q.; Solanki, A.; Jamaludin, N. F.; Lim, J. W. M.; Mathews, N.; Mhaisalkar, S.; Pshenichnikov, M. S.; Sum, T. C. Hot Carrier Extraction in $\text{CH}_3\text{NH}_3\text{PbI}_3$ Unveiled by Pump-Push-Probe Spectroscopy. *Sci. Adv.* **2019**, *5*, eaax3620.

(957) Dursun, I.; Maity, P.; Yin, J.; Turedi, B.; Zhumekenov, A. A.; Lee, K. J.; Mohammed, O. F.; Bakr, O. M. Why Are Hot Holes Easier to Extract than Hot Electrons from Methylammonium Lead Iodide Perovskite? *Adv. Energy Mater.* **2019**, *9*, 1900084.

(958) Shen, Q.; Ripolles, T. S.; Even, J.; Zhang, Y.; Ding, C.; Liu, F.; Izuishi, T.; Nakazawa, N.; Toyoda, T.; Ogomi, Y.; Hayase, S. Ultrafast Selective Extraction of Hot Holes from Cesium Lead Iodide Perovskite Films. *J. Energy Chem.* **2018**, *27*, 1170–1174.

(959) Evans, T. J. S.; Miyata, K.; Joshi, P. P.; Maehrlein, S.; Liu, F.; Zhu, X. Y. Competition Between Hot-Electron Cooling and Large Polaron Screening in CsPbBr_3 Perovskite Single Crystals. *J. Phys. Chem. C* **2018**, *122*, 13724–13730.

(960) Yang, J.; Wen, X.; Xia, H.; Sheng, R.; Ma, Q.; Kim, J.; Tapping, P.; Harada, T.; Kee, T. W.; Huang, F.; Cheng, Y.-B.; Green, M.; Ho-Baillie, A.; Huang, S.; Shrestha, S.; Patterson, R.; Conibeer, G. Acoustic-Optical Phonon Up-Conversion and Hot-Phonon Bottleneck in Lead-Halide Perovskites. *Nat. Commun.* **2017**, *8*, 14120.

(961) Boehme, S. C.; Brinck, S. T.; Maes, J.; Yazdani, N.; Zapata, F.; Chen, K.; Wood, V.; Hodgkiss, J. M.; Hens, Z.; Geiregat, P.; Infante, I. Phonon-Mediated and Weakly Size-Dependent Electron and Hole Cooling in CsPbBr_3 Nanocrystals Revealed by Atomistic Simulations and Ultrafast Spectroscopy. *Nano Lett.* **2020**, *20*, 1819–1829.

(962) Chouhan, L.; Ghimire, S.; Biju, V. Blinking Beats Bleaching: The Control of Superoxide Generation by Photo-Ionized Perovskite Nanocrystals. *Angew. Chem., Int. Ed.* **2019**, *58*, 4875–4879.

(963) Merdasa, A.; Tian, Y.; Camacho, R.; Dobrovolsky, A.; Debroye, E.; Unger, E. L.; Hofkens, J.; Sundström, V.; Scheblykin, I. G. “Supertrap” at Work: Extremely Efficient Nonradiative Recombination Channels in MAPbI_3 Perovskites Revealed by Luminescence Super-Resolution Imaging and Spectroscopy. *ACS Nano* **2017**, *11*, 5391–5404.

(964) Yuan, G.; Ritchie, C.; Ritter, M.; Murphy, S.; Gómez, D. E.; Mulvaney, P. The Degradation and Blinking of Single CsPbI_3 Perovskite Quantum Dots. *J. Phys. Chem. C* **2018**, *122*, 13407–13415.

(965) Galland, C.; Ghosh, Y.; Steinbrück, A.; Sykora, M.; Hollingsworth, J. A.; Klimov, V. I.; Htoon, H. Two Types of Luminescence Blinking Revealed by Spectroelectrochemistry of Single Quantum Dots. *Nature* **2011**, *479*, 203–207.

(966) Trinh, C. T.; Minh, D. N.; Ahn, K. J.; Kang, Y.; Lee, K.-G. Organic–Inorganic FaPbBr_3 Perovskite Quantum Dots as a Quantum Light Source: Single-Photon Emission and Blinking Behaviors. *ACS Photonics* **2018**, *5*, 4937–4943.

(967) Li, B.; Huang, H.; Zhang, G.; Yang, C.; Guo, W.; Chen, R.; Qin, C.; Gao, Y.; Biju, V. P.; Rogach, A. L.; Xiao, L.; Jia, S. Excitons and Biexciton Dynamics in Single CsPbBr_3 Perovskite Quantum Dots. *J. Phys. Chem. Lett.* **2018**, *9*, 6934–6940.

(968) Frantsuzov, P. A.; Marcus, R. A. Explanation of Quantum Dot Blinking Without the Long-Lived Trap Hypothesis. *Phys. Rev. B: Condens. Matter Mater. Phys.* **2005**, *72*, 155321.

(969) Frantsuzov, P. A.; Volkán-Kacsó, S.; Jankó, B. Model of Fluorescence Intermittency of Single Colloidal Semiconductor Quantum Dots Using Multiple Recombination Centers. *Phys. Rev. Lett.* **2009**, *103*, 207402.

(970) Kim, T.; Jung, S. I.; Ham, S.; Chung, H.; Kim, D. Elucidation of Photoluminescence Blinking Mechanism and Multiexciton Dynamics in Hybrid Organic–Inorganic Perovskite Quantum Dots. *Small* **2019**, *15*, 1900355.

(971) Seth, S.; Mondal, N.; Patra, S.; Samanta, A. Fluorescence Blinking and Photoactivation of All-Inorganic Perovskite Nanocrystals CsPbBr_3 and CsPbBr_2I . *J. Phys. Chem. Lett.* **2016**, *7*, 266–271.

(972) Yoshimura, H.; Yamauchi, M.; Masuo, S. *In Situ* Observation of Emission Behavior During Anion-Exchange Reaction of a Cesium Lead Halide Perovskite Nanocrystal at the Single-Nanocrystal Level. *J. Phys. Chem. Lett.* **2020**, *11*, 530–535.

(973) Chouhan, L.; Ito, S.; Thomas, E. M.; Takano, Y.; Ghimire, S.; Miyasaka, H.; Biju, V. Real-Time Blinking Suppression of Perovskite Quantum Dots by Halide Vacancy Filling. *ACS Nano* **2021**, *15*, 2831–2838.

(974) Tang, X.; Yang, J.; Li, S.; Liu, Z.; Hu, Z.; Hao, J.; Du, J.; Leng, Y.; Qin, H.; Lin, X.; Lin, Y.; Tian, Y.; Zhou, M.; Xiong, Q. Single Halide Perovskite/Semiconductor Core/Shell Quantum Dots with Ultrastability and Nonblinking Properties. *Adv. Sci.* **2019**, *6*, 1900412.

(975) Sharma, D. K.; Hirata, S.; Biju, V.; Vacha, M. Stark Effect and Environment-Induced Modulation of Emission in Single Halide Perovskite Nanocrystals. *ACS Nano* **2019**, *13*, 624–632.

(976) Tian, Y.; Merdasa, A.; Peter, M.; Abdellah, M.; Zheng, K.; Ponceca, C. S.; Pullerits, T.; Yartsev, A.; Sundström, V.; Scheblykin, I. G. Giant Photoluminescence Blinking of Perovskite Nanocrystals Reveals Single-Trap Control of Luminescence. *Nano Lett.* **2015**, *15*, 1603–1608.

(977) Gerhard, M.; Louis, B.; Camacho, R.; Merdasa, A.; Li, J.; Kiligridis, A.; Dobrovolsky, A.; Hofkens, J.; Scheblykin, I. G. Microscopic Insight into Non-Radiative Decay in Perovskite Semiconductors from Temperature-Dependent Luminescence Blinking. *Nat. Commun.* **2019**, *10*, 1698.

(978) Scheblykin, I. G. Small Number of Defects Per Nanostructure Leads to “Digital” Quenching of Photoluminescence: The Case of Metal Halide Perovskites. *Adv. Energy Mater.* **2020**, *10*, 2001724.

(979) Yuan, H.; Debroye, E.; Caliandro, G.; Janssen, K. P. F.; Van Loon, J.; Kirschhock, C. E. A.; Martens, J. A.; Hofkens, J.; Roeffaers, M. B. J. Photoluminescence Blinking of Single-Crystal Methylammonium Lead Iodide Perovskite Nanorods Induced by Surface Traps. *ACS Omega* **2016**, *1*, 148–159.

(980) Eremchev, I. Y.; Tarasevich, A. O.; Li, J.; Naumov, A. V.; Scheblykin, I. G. Lack of Photon Antibunching Supports Supertrap Model of Photoluminescence Blinking in Perovskite Sub-Micrometer Crystals. *Adv. Opt. Mater.* **2021**, *9*, 2001596.

(981) Wen, X.; Ho-Baillie, A.; Huang, S.; Sheng, R.; Chen, S.; Ko, H.-C.; Green, M. A. Mobile Charge-Induced Fluorescence Intermittency in Methylammonium Lead Bromide Perovskite. *Nano Lett.* **2015**, *15*, 4644–4649.

(982) Freppon, D. J.; Men, L.; Burkhow, S. J.; Petrich, J. W.; Vela, J.; Smith, E. A. Photophysical Properties of Wavelength-Tunable Methylammonium Lead Halide Perovskite Nanocrystals. *J. Mater. Chem. C* **2017**, *5*, 118–126.

(983) Tachikawa, T.; Karimata, I.; Kobori, Y. Surface Charge Trapping in Organolead Halide Perovskites Explored by Single-Particle Photoluminescence Imaging. *J. Phys. Chem. Lett.* **2015**, *6*, 3195–3201.

(984) Halder, A.; Chulliyil, R.; Subbiah, A. S.; Khan, T.; Chattoraj, S.; Chowdhury, A.; Sarkar, S. K. Pseudohalide (SCN^-)-Doped MAPbI_3 Perovskites: A Few Surprises. *J. Phys. Chem. Lett.* **2015**, *6*, 3483–3489.

(985) Li, C.; Zhong, Y.; Luna, C. A.; Unger, T.; Deichsel, K.; Gräser, A.; Köhler, J.; Köhler, A.; Hildner, R.; Huettner, S. Emission Enhancement and Intermittency in Polycrystalline Organolead Halide Perovskite Films. *Molecules* **2016**, *21*, 1081.

(986) Tian, Y.; Merdasa, A.; Unger, E.; Abdellah, M.; Zheng, K.; McKibbin, S.; Mikkelsen, A.; Pullerits, T.; Yartsev, A.; Sundström, V.; Scheblykin, I. G. Enhanced Organo-Metal Halide Perovskite Photoluminescence from Nanosized Defect-Free Crystallites and Emitting Sites. *J. Phys. Chem. Lett.* **2015**, *6*, 4171–4177.

(987) Yuan, H.; Debroye, E.; Bladt, E.; Lu, G.; Keshavarz, M.; Janssen, K. P. F.; Roeffaers, M. B. J.; Bals, S.; Sargent, E. H.; Hofkens, J. Imaging Heterogeneously Distributed Photo-Active Traps in Perovskite Single Crystals. *Adv. Mater.* **2018**, *30*, 1705494.

(988) Lee, S.; Park, J. H.; Lee, B. R.; Jung, E. D.; Yu, J. C.; Di Nuzzo, D.; Friend, R. H.; Song, M. H. Amine-Based Passivating Materials for Enhanced Optical Properties and Performance of Organic–Inorganic Perovskites in Light-Emitting Diodes. *J. Phys. Chem. Lett.* **2017**, *8*, 1784–1792.

(989) Halder, A.; Pathoor, N.; Chowdhury, A.; Sarkar, S. K. Photoluminescence Flickering of Micron-Sized Crystals of Methylammonium Lead Bromide: Effect of Ambience and Light Exposure. *J. Phys. Chem. C* **2018**, *122*, 15133–15139.

(990) Sharma, D. K.; Hirata, S.; Vacha, M. Single-Particle Electroluminescence of CsPbBr_3 Perovskite Nanocrystals Reveals Particle-Selective Recombination and Blinking as Key Efficiency Factors. *Nat. Commun.* **2019**, *10*, 4499.

(991) Herz, L. M. Charge-Carrier Mobilities in Metal Halide Perovskites: Fundamental Mechanisms and Limits. *ACS Energy Lett.* **2017**, *2*, 1539–1548.

(992) Pérez-Osorio, M. A.; Milot, R. L.; Filip, M. R.; Patel, J. B.; Herz, L. M.; Johnston, M. B.; Giustino, F. Vibrational Properties of the Organic–Inorganic Halide Perovskite $\text{CH}_3\text{NH}_3\text{PbI}_3$ from Theory and Experiment: Factor Group Analysis, First-Principles Calculations, and Low-Temperature Infrared Spectra. *J. Phys. Chem. C* **2015**, *119*, 25703–25718.

(993) Brivio, F.; Frost, J. M.; Skelton, J. M.; Jackson, A. J.; Weber, O. J.; Weller, M. T.; Goñi, A. R.; Leguy, A. M. A.; Barnes, P. R. F.; Walsh, A. Lattice Dynamics and Vibrational Spectra of the Orthorhombic, Tetragonal, and Cubic Phases of Methylammonium Lead Iodide. *Phys. Rev. B: Condens. Matter Mater. Phys.* **2015**, *92*, 144308.

(994) Clinckemalie, L.; Valli, D.; Roeffaers, M. B. J.; Hofkens, J.; Pradhan, B.; Debroye, E. Challenges and Opportunities for CsPbBr_3 Perovskites in Low- and High-Energy Radiation Detection. *ACS Energy Lett.* **2021**, *6*, 1290–1314.

(995) Keshavarz, M.; Debroye, E.; Ottesen, M.; Martin, C.; Zhang, H.; Fron, E.; KÜChler, R.; Steele, J. A.; Bremholm, M.; Van De Vondel, J.; Wang, H. I.; Bonn, M.; Roeffaers, M. B. J.; Wiedmann, S.; Hofkens, J. Tuning the Structural and Optoelectronic Properties of $\text{Cs}_2\text{AgBiBr}_6$ Double-Perovskite Single Crystals through Alkali-Metal Substitution. *Adv. Mater.* **2020**, *32*, 2001878.

(996) Steele, J. A.; Puech, P.; Monserrat, B.; Wu, B.; Yang, R. X.; Kirchartz, T.; Yuan, H.; Fleury, G.; Giovanni, D.; Fron, E.; Keshavarz, M.; Debroye, E.; Zhou, G.; Sum, T. C.; Walsh, A.; Hofkens, J.; Roeffaers, M. B. J. Role of Electron–Phonon Coupling in the Thermal Evolution of Bulk Rashba-Like Spin-Split Lead Halide Perovskites Exhibiting Dual-Band Photoluminescence. *ACS Energy Lett.* **2019**, *4*, 2205–2212.

(997) Fu, M.; Tamarat, P.; Trebbia, J.-B.; Bodnarchuk, M. I.; Kovalenko, M. V.; Even, J.; Lounis, B. Unraveling Exciton–Phonon Coupling in Individual FaPbI_3 Nanocrystals Emitting Near-Infrared Single Photons. *Nat. Commun.* **2018**, *9*, 3318.

(998) Becker, M. A.; Scarpelli, L.; Nedelcu, G.; Rainò, G.; Masia, F.; Borri, P.; Stöferle, T.; Kovalenko, M. V.; Langbein, W.; Mahrt, R. F. Long Exciton Dephasing Time and Coherent Phonon Coupling in CsPbBr_2Cl Perovskite Nanocrystals. *Nano Lett.* **2018**, *18*, 7546–7551.

(999) Sychugov, I.; Juhasz, R.; Valenta, J.; Linnros, J. Narrow Luminescence Linewidth of a Silicon Quantum Dot. *Phys. Rev. Lett.* **2005**, *94*, 087405.

(1000) Rainò, G.; Nedelcu, G.; Protesescu, L.; Bodnarchuk, M. I.; Kovalenko, M. V.; Mahrt, R. F.; Stöferle, T. Single Cesium Lead Halide Perovskite Nanocrystals at Low Temperature: Fast Single-Photon Emission, Reduced Blinking, and Exciton Fine Structure. *ACS Nano* **2016**, *10*, 2485–2490.

(1001) Pfingsten, O.; Klein, J.; Protesescu, L.; Bodnarchuk, M. I.; Kovalenko, M. V.; Bacher, G. Phonon Interaction and Phase Transition in Single Formamidinium Lead Bromide Quantum Dots. *Nano Lett.* **2018**, *18*, 4440–4446.

(1002) Ramade, J.; Andriambariariaona, L. M.; Steinmetz, V.; Goubet, N.; Legrand, L.; Barisien, T.; Bernardot, F.; Testelin, C.; Lhuillier, E.; Bramati, A.; Chamarro, M. Exciton–Phonon Coupling in a CsPbBr_3 Single Nanocrystal. *Appl. Phys. Lett.* **2018**, *112*, 072104.

(1003) Liu, L.; Pevere, F.; Zhang, F.; Zhong, H.; Sychugov, I. Cation Effect on Excitons in Perovskite Nanocrystals from Single-dot Photoluminescence of $\text{CH}_3\text{NH}_3\text{PbI}_3$. *Phys. Rev. B: Condens. Matter Mater. Phys.* **2019**, *100*, 195430.

(1004) Miyata, K.; Atallah, T. L.; Zhu, X.-Y. Lead Halide Perovskites: Crystal–Liquid Duality, Phonon Glass Electron Crystals, and Large Polaron Formation. *Sci. Adv.* **2017**, *3*, e1701469.

(1005) Scamarcio, G.; Spagnolo, V.; Ventrucci, G.; Lugará, M.; Righini, G. C. Size Dependence of Electron–LO–Phonon Coupling in Semiconductor Nanocrystals. *Phys. Rev. B: Condens. Matter Mater. Phys.* **1996**, *53*, R10489–R10492.

(1006) Zhao, Z.; Zhong, M.; Zhou, W.; Peng, Y.; Yin, Y.; Tang, D.; Zou, B. Simultaneous Triplet Exciton–Phonon and Exciton–Photon Photoluminescence in the Individual Weak Confinement CsPbBr_3 Micro/Nanowires. *J. Phys. Chem. C* **2019**, *123*, 25349–25358.

(1007) Nie, W.; Blancon, J.-C.; Neukirch, A. J.; Appavoo, K.; Tsai, H.; Chhowalla, M.; Alam, M. A.; Sfeir, M. Y.; Katan, C.; Even, J.; Tretiak, S.; Crochet, J. J.; Gupta, G.; Mohite, A. D. Light-Activated Photocurrent Degradation and Self-healing in Perovskite Solar Cells. *Nat. Commun.* **2016**, *7*, 11574.

(1008) Petruska, M. A.; Malko, A. V.; Voyles, P. M.; Klimov, V. I. High Performance Quantum Dot Nanocomposites for Nonlinear Optical and Optical Gain Applications. *Adv. Mater.* **2003**, *15*, 610–613.

(1009) Mi, Y.; Zhong, Y.; Zhang, Q.; Liu, X. Continuous Wave Pumped Perovskite Lasers. *Adv. Opt. Mater.* **2019**, *7*, 1900544.

(1010) Yakunin, S.; Protesescu, L.; Krieg, F.; Bodnarchuk, M. I.; Nedelcu, G.; Humer, M.; De Luca, G.; Fiebig, M.; Heiss, W.; Kovalenko, M. V. Low-Threshold Amplified Spontaneous Emission and Lasing from Colloidal Nanocrystals of Caesium Lead Halide Perovskites. *Nat. Commun.* **2015**, *6*, 8056.

(1011) Wang, Y.; Li, X.; Zhao, X.; Xiao, L.; Zeng, H.; Sun, H. Nonlinear Absorption and Low-Threshold Multiphoton Pumped Stimulated Emission from All-Inorganic Perovskite Nanocrystals. *Nano Lett.* **2016**, *16*, 448–453.

(1012) Eisler, H.-J.; Sundar, V. C.; Bawendi, M. G.; Walsh, M.; Smith, H. I.; Klimov, V. Color-Selective Semiconductor Nanocrystal Laser. *Appl. Phys. Lett.* **2002**, *80*, 4614–4616.

(1013) Dai, X.; Deng, Y.; Peng, X.; Jin, Y. Quantum Dot Light Emitting Diodes for Large Area Displays: Towards the Dawn of Commercialization. *Adv. Mater.* **2017**, *29*, 1607022.

(1014) Wang, Y.; Li, X.; Nalla, V.; Zeng, H.; Sun, H. Solution Processed Low Threshold Vertical Cavity Surface Emitting Lasers from All Inorganic Perovskite Nanocrystals. *Adv. Funct. Mater.* **2017**, *27*, 1605088.

(1015) Kambhampati, P. Hot Exciton Relaxation Dynamics in Semiconductor Quantum Dots: Radiationless Transitions on the Nanoscale. *J. Phys. Chem. C* **2011**, *115*, 22089–22109.

(1016) She, C.; Fedin, I.; Dolzhnikov, D. S.; Demortière, A.; Schaller, R. D.; Pelton, M.; Talapin, D. V. Low Threshold Stimulated Emission using Colloidal Quantum Wells. *Nano Lett.* **2014**, *14*, 2772–2777.

(1017) Grim, J. Q.; Christodoulou, S.; Di Stasio, F.; Krahne, R.; Cingolani, R.; Manna, L.; Moreels, I. Continuous Wave Biexciton Lasing at Room Temperature using Solution Processed Quantum Wells. *Nat. Nanotechnol.* **2014**, *9*, 891.

(1018) Garcia-Santamaría, F.; Chen, Y.; Vela, J.; Schaller, R. D.; Hollingsworth, J. A.; Klimov, V. I. Suppressed Auger Recombination in “Giant” Nanocrystals Boosts optical Gain Performance. *Nano Lett.* **2009**, *9*, 3482–3488.

(1019) Shi, Z. F.; Sun, X. G.; Wu, D.; Xu, T. T.; Tian, Y. T.; Zhang, Y. T.; Li, X. J.; Du, G. T. Near-Infrared Random Lasing Realized in a Perovskite $\text{CH}_3\text{NH}_3\text{PbI}_3$ Thin Film. *J. Mater. Chem. C* **2016**, *4*, 8373–8379.

(1020) Xu, Y.; Chen, Q.; Zhang, C.; Wang, R.; Wu, H.; Zhang, X.; Xing, G.; Yu, W. W.; Wang, X.; Zhang, Y.; Xiao, M. Two-Photon-Pumped Perovskite Semiconductor Nanocrystal Lasers. *J. Am. Chem. Soc.* **2016**, *138*, 3761–3768.

(1021) Jia, Y.; Kerner, R. A.; Grede, A. J.; Brigeman, A. N.; Rand, B. P.; Giebink, N. C. Diode-Pumped Organo-Lead Halide Perovskite Lasing in a Metal-Clad Distributed Feedback Resonator. *Nano Lett.* **2016**, *16*, 4624–4629.

(1022) Harwell, J. R.; Whitworth, G. L.; Turnbull, G. A.; Samuel, I. D. W. Green Perovskite Distributed Feedback Lasers. *Sci. Rep.* **2017**, *7*, 11727.

(1023) Mathies, F.; Brenner, P.; Hernandez-Sosa, G.; Howard, I. A.; Paetzold, U. W.; Lemmer, U. Inkjet-Printed Perovskite Distributed Feedback Lasers. *Opt. Express* **2018**, *26*, A144–A152.

(1024) Tian, C.; Guo, T.; Zhao, S.; Zhai, W.; Ge, C.; Ran, G. Low-Threshold Room-Temperature Continuous-Wave Optical Lasing of Single-Crystalline Perovskite in a Distributed Referencelector Microcavity. *RSC Adv.* **2019**, *9*, 35984–35989.

(1025) Chen, S.; Zhang, C.; Lee, J.; Han, J.; Nurmikko, A. High-Q Low-Threshold Monolithic Perovskite Thin-Film Vertical-Cavity Lasers. *Adv. Mater.* **2017**, *29*, 1604781.

(1026) Bar-On, O.; Brenner, P.; Lemmer, U.; Scheuer, J. In Perovskite Micro Laser Arrays using Scalable Lithography: Towards Integrated Perovskite Photonics. *CLEO: Science and Innovations, Optical Society of America* **2019**, SF2J. 2.

(1027) Wang, S.; Yu, J.; Zhang, M.; Chen, D.; Li, C.; Chen, R.; Jia, G.; Rogach, A. L.; Yang, X. Stable, Strongly Emitting Cesium Lead Bromide Perovskite Nanorods with High Optical Gain Enabled by an Intermediate Monomer Reservoir Synthetic Strategy. *Nano Lett.* **2019**, *19*, 6315–6322.

(1028) Wang, Y.; Zhi, M.; Chang, Y.-Q.; Zhang, J.-P.; Chan, Y. Stable, Ultralow Threshold Amplified Spontaneous Emission from CsPbBr_3 Nanoparticles Exhibiting Trion Gain. *Nano Lett.* **2018**, *18*, 4976–4984.

(1029) Pramanik, A.; Gates, K.; Gao, Y.; Begum, S.; Chandra Ray, P. Several Orders-of-Magnitude Enhancement of Multiphoton Absorption Property for CsPbX_3 Perovskite Quantum Dots by Manipulating Halide Stoichiometry. *J. Phys. Chem. C* **2019**, *123*, 5150–5156.

(1030) Wei, S.; Yang, Y.; Kang, X.; Wang, L.; Huang, L.; Pan, D. Room-Temperature and Gram-Scale Synthesis of CsPbX_3 (X= Cl, Br, I) Perovskite Nanocrystals with 50–85% Photoluminescence Quantum Yields. *Chem. Commun.* **2016**, *52*, 7265–7268.

(1031) Xing, G.; Mathews, N.; Lim, S. S.; Yantara, N.; Liu, X.; Sabba, D.; Grätzel, M.; Mhaisalkar, S.; Sum, T. C. Low-Temperature Solution-Processed Wavelength-Tunable Perovskites for Lasing. *Nat. Mater.* **2014**, *13*, 476.

(1032) Balena, A.; Perulli, A.; Fernandez, M.; De Giorgi, M. L.; Nedelcu, G.; Kovalenko, M. V.; Anni, M. Temperature Dependence of the Amplified Spontaneous Emission from CsPbBr_3 Nanocrystal Thin Films. *J. Phys. Chem. C* **2018**, *122*, 5813–5819.

(1033) Tan, M. J.; Wang, Y.; Chan, Y. Solution-Based Green Amplified Spontaneous Emission from Colloidal Perovskite Nanocrystals Exhibiting High Stability. *Appl. Phys. Lett.* **2019**, *114*, 183101.

(1034) Zhao, W.; Qin, Z.; Zhang, C.; Wang, G.; Huang, X.; Li, B.; Dai, X.; Xiao, M. Optical Gain from Biexcitons in CsPbBr_3 Nanocrystals Revealed by Two-dimensional Electronic Spectroscopy. *J. Phys. Chem. Lett.* **2019**, *10*, 1251–1258.

(1035) Navarro-Arenas, J.; Suárez, I.; Chirvony, V. S.; Gualdrón-Reyes, A. F.; Mora-Seró, I.; Martínez-Pastor, J. Single-Exciton Amplified Spontaneous Emission in Thin Films of CsPbX_3 (X= Br, I) Perovskite Nanocrystals. *J. Phys. Chem. Lett.* **2019**, *10*, 6389–6398.

(1036) Stylianakis, M. M.; Maksudov, T.; Panagiotopoulos, A.; Kakavelakis, G.; Petridis, K. Inorganic and Hybrid Perovskite Based Laser Devices: A Review. *Materials* **2019**, *12*, 859.

(1037) De Giorgi, M. L.; Anni, M. Amplified Spontaneous Emission and Lasing in Lead Halide Perovskites: State of the Art and Perspectives. *Appl. Sci.* **2019**, *9*, 4591.

(1038) Nagamine, G.; Rocha, J. O.; Bonato, L. G.; Nogueira, A. F.; Zaharieva, Z.; Watt, A. A.; de Brito Cruz, C. H.; Padilha, L. A. Two-Photon Absorption and Two-Photon-Induced Gain in Perovskite Quantum Dots. *J. Phys. Chem. Lett.* **2018**, *9*, 3478–3484.

(1039) Wang, Y.; Yang, X.; He, T.; Gao, Y.; Demir, H. V.; Sun, X.; Sun, H. Near Resonant and Nonresonant Third-order Optical Nonlinearities of Colloidal InP/ZnS Quantum Dots. *Appl. Phys. Lett.* **2013**, *102*, 021917.

(1040) He, G. S.; Tan, L.-S.; Zheng, Q.; Prasad, P. N. Multiphoton Absorbing Materials: Molecular Designs, Characterizations, and Applications. *Chem. Rev.* **2008**, *108*, 1245–1330.

(1041) Jasieniak, J. J.; Fortunati, I.; Gardin, S.; Signorini, R.; Bozio, R.; Martucci, A.; Mulvaney, P. Highly Efficient Amplified Stimulated Emission from CdSe-CdS-ZnS Quantum Dot Doped Waveguides with Two-Photon Infrared Optical Pumping. *Adv. Mater.* **2008**, *20*, 69–73.

(1042) Veldhuis, S. A.; Tay, Y. K. E.; Bruno, A.; Dintakurti, S. S.; Bhawmik, S.; Muduli, S. K.; Li, M.; Mathews, N.; Sum, T. C.; Mhaisalkar, S. G. Benzyl Alcohol-Treated $\text{CH}_3\text{NH}_3\text{PbBr}_3$ Nanocryst- als Exhibiting High Luminescence, Stability, and Ultralow Amplified Spontaneous Emission Thresholds. *Nano Lett.* **2017**, *17*, 7424–7432.

(1043) She, C.; Fedin, I.; Dolzhnikov, D. S.; Dahlberg, P. D.; Engel, G. S.; Schaller, R. D.; Talapin, D. V. Red, Yellow, Green, and Blue Amplified Spontaneous Emission and Lasing Using Colloidal CdSe Nanoplatelets. *ACS Nano* **2015**, *9*, 9475–9485.

(1044) Yuan, F.; Wu, Z.; Dong, H.; Xi, J.; Xi, K.; Divitini, G.; Jiao, B.; Hou, X.; Wang, S.; Gong, Q. High Stability and Ultralow Threshold Amplified Spontaneous Emission from Formamidinium Lead Halide Perovskite Films. *J. Phys. Chem. C* **2017**, *121*, 15318–15325.

(1045) Trots, D.; Myagkota, S. High-Temperature Structural Evolution of Caesium and Rubidium Triiodoplumbates. *J. Phys. Chem. Solids* **2008**, *69*, 2520–2526.

(1046) Stoumpos, C. C.; Malliakas, C. D.; Kanatzidis, M. G. Semiconducting Tin and Lead Iodide Perovskites with Organic Cations: Phase Transitions, High Mobilities, and Near-Infrared Photoluminescent Properties. *Inorg. Chem.* **2013**, *52*, 9019–9038.

(1047) Liu, Z.; Hu, Z.; Zhang, Z.; Du, J.; Yang, J.; Tang, X.; Liu, W.; Leng, Y. Two-Photon Pumped Amplified Spontaneous Emission and Lasing from Formamidinium Lead Bromine Nanocrystals. *ACS Photonics* **2019**, *6*, 3150–3158.

(1048) Dhanker, R.; Brigeman, A.; Larsen, A.; Stewart, R.; Asbury, J. B.; Giebink, N. C. Random Lasing in Organo-Lead Halide Perovskite Microcrystal Networks. *Appl. Phys. Lett.* **2014**, *105*, 151112.

(1049) Li, C.; Zang, Z.; Han, C.; Hu, Z.; Tang, X.; Du, J.; Leng, Y.; Sun, K. Highly Compact CsPbBr_3 Perovskite Thin Films Decorated by ZnO Nanoparticles for Enhanced Random Lasing. *Nano Energy* **2017**, *40*, 195–202.

(1050) Roy, P. K.; Haider, G.; Lin, H. I.; Liao, Y. M.; Lu, C. H.; Chen, K. H.; Chen, L. C.; Shih, W. H.; Liang, C. T.; Chen, Y. F. Multicolor Ultralow-Threshold Random Laser Assisted by Vertical-Graphene Network. *Adv. Opt. Mater.* **2018**, *6*, 1800382.

(1051) Huang, C.-Y.; Zou, C.; Mao, C.; Corp, K. L.; Yao, Y.-C.; Lee, Y.-J.; Schlenker, C. W.; Jen, A. K.; Lin, L. Y. CsPbBr_3 Perovskite Quantum Dot Vertical Cavity Lasers with Low Threshold and High Stability. *ACS Photonics* **2017**, *4*, 2281–2289.

(1052) Malko, A.; Mikhailovsky, A.; Petruska, M.; Hollingsworth, J.; Htoon, H.; Bawendi, M.; Klimov, V. I. From Amplified Spontaneous Emission to Microring Lasing using Nanocrystal Quantum Dot Solids. *Appl. Phys. Lett.* **2002**, *81*, 1303–1305.

(1053) Kazes, M.; Lewis, D. Y.; Ebenstein, Y.; Mokari, T.; Banin, U. Lasing from Semiconductor Quantum Rods in a Cylindrical Microcavity. *Adv. Mater.* **2002**, *14*, 317–321.

(1054) Tang, B.; Dong, H.; Sun, L.; Zheng, W.; Wang, Q.; Sun, F.; Jiang, X.; Pan, A.; Zhang, L. Single-Mode Lasers Based on Cesium Lead Halide Perovskite Submicron Spheres. *ACS Nano* **2017**, *11*, 10681–10688.

(1055) Kurahashi, N.; Nguyen, V.-C.; Sasaki, F.; Yanagi, H. Whispering Gallery Mode Lasing in Lead Halide Perovskite Crystals Grown in Microcapillary. *Appl. Phys. Lett.* **2018**, *113*, 011107.

(1056) Liu, Z.; Hu, Z.; Shi, T.; Du, J.; Yang, J.; Zhang, Z.; Tang, X.; Leng, Y. Stable and Enhanced Frequency Up-Converted Lasing from CsPbBr_3 Quantum Dots Embedded in Silica Sphere. *Opt. Express* **2019**, *27*, 9459–9466.

(1057) Stranks, S. D.; Wood, S. M.; Wojciechowski, K.; Deschler, F.; Saliba, M.; Khandelwal, H.; Patel, J. B.; Elston, S. J.; Herz, L. M.; Johnston, M. B.; Schenning, A. P. H. J.; Debije, M. G.; Riede, M. K.; Morris, S. M.; Snaith, H. J. Enhanced Amplified Spontaneous Emission in Perovskites using a Flexible Cholesteric Liquid Crystal referencelector. *Nano Lett.* **2015**, *15*, 4935–4941.

(1058) Folie, B. D.; Tan, J. A.; Huang, J. M.; Sercel, P. C.; Delor, M.; Lai, M. L.; Lyons, J. L.; Bernstein, N.; Efros, A. L.; Yang, P. D.; Ginsberg, N. S. Effect of Anisotropic Confinement on Electronic Structure and Dynamics of Band Edge Excitons in Inorganic Perovskite Nanowires. *J. Phys. Chem. A* **2020**, *124*, 1867–1876.

(1059) Janker, L.; Tong, Y.; Polavarapu, L.; Feldmann, J.; Urban, A. S.; Krenner, H. J. Real-Time Electron and Hole Transport Dynamics in Halide Perovskite Nanowires. *Nano Lett.* **2019**, *19*, 8701–8707.

(1060) Fu, Y. P.; Zhu, H. M.; Stoumpos, C. C.; Ding, Q.; Wang, J.; Kanatzidis, M. G.; Zhu, X. Y.; Jin, S. Broad Wavelength Tunable Robust Lasing from Single-Crystal Nanowires of Cesium Lead Halide Perovskites (CsPbX_3 , X = Cl, Br, I). *ACS Nano* **2016**, *10*, 7963–7972.

(1061) Park, K.; Lee, J. W.; Kim, J. D.; Han, N. S.; Jang, D. M.; Jeong, S.; Park, J.; Song, J. K. Light-Matter Interactions in Cesium Lead Halide Perovskite Nanowire Lasers. *J. Phys. Chem. Lett.* **2016**, *7*, 3703–10.

(1062) Wang, X.; Shoaib, M.; Wang, X.; Zhang, X.; He, M.; Luo, Z.; Zheng, W.; Li, H.; Yang, T.; Zhu, X.; Ma, L.; Pan, A. High-Quality In-Plane Aligned CsPbX_3 Perovskite Nanowire Lasers with Composition-Dependent Strong Exciton-Photon Coupling. *ACS Nano* **2018**, *12*, 6170–6178.

(1063) Xing, J.; Liu, X. F.; Zhang, Q.; Ha, S. T.; Yuan, Y. W.; Shen, C.; Sum, T. C.; Xiong, Q. Vapor Phase Synthesis of Organometal Halide Perovskite Nanowires for Tunable Room-Temperature Nanolasers. *Nano Lett.* **2015**, *15*, 4571–4577.

(1064) Shang, Q.; Zhang, S.; Liu, Z.; Chen, J.; Yang, P.; Li, C.; Li, W.; Zhang, Y.; Xiong, Q.; Liu, X.; Zhang, Q. Surface Plasmon Enhanced Strong Exciton-Photon Coupling in Hybrid Inorganic-Organic Perovskite Nanowires. *Nano Lett.* **2018**, *18*, 3335–3343.

(1065) Schlaus, A. P.; Spencer, M. S.; Miyata, K.; Liu, F.; Wang, X. X.; Datta, I.; Lipson, M.; Pan, A. L.; Zhu, X. Y. How Lasing Happens in CsPbBr_3 Perovskite Nanowires. *Nat. Commun.* **2019**, *10*, 265.

(1066) Zhang, X.; Lin, H.; Huang, H.; Reckmeier, C.; Zhang, Y.; Choy, W. C.; Rogach, A. L. Enhancing the Brightness of Cesium Lead Halide Perovskite Nanocrystal Based Green Light-Emitting Devices Through the Interface Engineering with Perfluorinated Ionomer. *Nano Lett.* **2016**, *16*, 1415–1420.

(1067) Chen, J.; Liu, D.; Al-Marri, M. J.; Nuuttila, L.; Lehtivuori, H.; Zheng, K. Photo-Stability of CsPbBr_3 Perovskite Quantum Dots for Optoelectronic Application. *Sci. China Mater.* **2016**, *59*, 719–727.

(1068) Li, X.; Wang, Y.; Sun, H.; Zeng, H. Amino-Mediated Anchoring Perovskite Quantum Dots for Stable and Low-Threshold Random Lasing. *Adv. Mater.* **2017**, *29*, 1701185.

(1069) Jia, Y.; Kerner, R. A.; Grede, A. J.; Rand, B. P.; Giebink, N. C. Continuous-Wave Lasing in an Organic-Inorganic Lead Halide Perovskite Semiconductor. *Nat. Photonics* **2017**, *11*, 784.

(1070) Evans, T. J.; Schlaus, A.; Fu, Y.; Zhong, X.; Atallah, T. L.; Spencer, M. S.; Brus, L. E.; Jin, S.; Zhu, X. Y. Continuous-Wave Lasing in Cesium Lead Bromide Perovskite Nanowires. *Adv. Opt. Mater.* **2018**, *6*, 1700982.

(1071) Chen, J.; Du, W.; Shi, J.; Li, M.; Wang, Y.; Zhang, Q.; Liu, X. Perovskite Quantum Dot Lasers. *InfoMat* **2020**, *2*, 170–183.

(1072) Wang, Y.; Sun, H. Advances and Prospects of Lasers Developed from Colloidal Semiconductor Nanostructures. *Prog. Quantum Electron.* **2018**, *60*, 1–29.

(1073) Pietryga, J. M.; Park, Y.-S.; Lim, J.; Fidler, A. F.; Bae, W. K.; Brovelli, S.; Klimov, V. I. Spectroscopic and Device Aspects of Nanocrystal Quantum Dots. *Chem. Rev.* **2016**, *116*, 10513–10622.

(1074) Hong, X.; Ishihara, T.; Nurmikko, A. V. Photoconductivity and Electroluminescence in Lead Iodide Based Natural Quantum Well Structures. *Solid State Commun.* **1992**, *84*, 657–661.

(1075) Hattori, T.; Taira, T.; Era, M.; Tsutsui, T.; Saito, S. Highly Efficient Electroluminescence from a Heterostructure Device Combined with Emissive Layered-Perovskite and an Electron-Transporting Organic Compound. *Chem. Phys. Lett.* **1996**, *254*, 103–108.

(1076) Chondroudis, K.; Mitzi, D. B. Electroluminescence from an Organic-Inorganic Perovskite Incorporating a Quaterthiophene Dye within Lead Halide Perovskite Layers. *Chem. Mater.* **1999**, *11*, 3028–3030.

(1077) Heo, J. H.; Im, S. H.; Noh, J. H.; Mandal, T. N.; Lim, C.-S.; Chang, J. A.; Lee, Y. H.; Kim, H.-j.; Sarkar, A.; Nazeeruddin, M. K.; Grätzel, M.; Seok, S. I. Efficient Inorganic-Organic Hybrid Heterojunction Solar Cells Containing Perovskite Compound and Polymeric Hole Conductors. *Nat. Photonics* **2013**, *7*, 486–491.

(1078) Chiba, T.; Hayashi, Y.; Ebe, H.; Hoshi, K.; Sato, J.; Sato, S.; Pu, Y.-J.; Ohisa, S.; Kido, J. Anion-Exchange Red Perovskite Quantum Dots with Ammonium Iodine Salts for Highly Efficient Light-Emitting Devices. *Nat. Photonics* **2018**, *12*, 681–687.

(1079) Zhao, B.; Bai, S.; Kim, V.; Lamboll, R.; Shivanna, R.; Auras, F.; Richter, J. M.; Yang, L.; Dai, L.; Alsari, M.; She, X.-J.; Liang, L.; Zhang, J.; Lilliu, S.; Gao, P.; Snaith, H. J.; Wang, J.; Greenham, N. C.; Friend, R. H.; Di, D. High-Efficiency Perovskite-Polymer Bulk Heterostructure Light-Emitting Diodes. *Nat. Photonics* **2018**, *12*, 783–789.

(1080) Tress, W. Metal Halide Perovskites as Mixed Electronic-Ionic Conductors: Challenges and Opportunities-From Hysteresis to Memristivity. *J. Phys. Chem. Lett.* **2017**, *8*, 3106–3114.

(1081) Govinda, S.; Kore, B. P.; Bokdam, M.; Mahale, P.; Kumar, A.; Pal, S.; Bhattacharya, B.; Lahnsteiner, J.; Kresse, G.; Franchini, C.; Pandey, A.; Sarma, D. D. Behavior of Methylammonium Dipoles in MAPbX_3 (X = Br and I). *J. Phys. Chem. Lett.* **2017**, *8*, 4113–4121.

(1082) Xing, J.; Zhao, Y.; Askerka, M.; Quan, L. N.; Gong, X.; Zhao, W.; Zhao, J.; Tan, H.; Long, G.; Gao, L.; Yang, Z.; Voznyy, O.; Tang, J.; Lu, Z.-H.; Xiong, Q.; Sargent, E. H. Color-Stable Highly Luminescent Sky-Blue Perovskite Light-Emitting Diodes. *Nat. Commun.* **2018**, *9*, 3541.

(1083) Xing, J.; Yan, F.; Zhao, Y.; Chen, S.; Yu, H.; Zhang, Q.; Zeng, R.; Demir, H. V.; Sun, X.; Huan, A.; Xiong, Q. High-Efficiency Light-Emitting Diodes of Organometal Halide Perovskite Amorphous Nanoparticles. *ACS Nano* **2016**, *10*, 6623–6630.

(1084) Tong, J.; Wu, J.; Shen, W.; Zhang, Y.; Liu, Y.; Zhang, T.; Nie, S.; Deng, Z. Direct Hot-Injection Synthesis of Lead Halide Perovskite Nanocubes in Acrylic Monomers for Ultrastable and Bright Nanocrystal-Polymer Composite Films. *ACS Appl. Mater. Interfaces* **2019**, *11*, 9317–9325.

(1085) Yan, F.; Demir, H. V. LEDs using Halide Perovskite Nanocrystal Emitters. *Nanoscale* **2019**, *11*, 11402–11412.

(1086) Kim, G. Y.; Senocrate, A.; Yang, T. Y.; Gregori, G.; Gratzel, M.; Maier, J. Large Tunable Photoeffect on Ion Conduction in Halide Perovskites and Implications for Photodecomposition. *Nat. Mater.* **2018**, *17*, 445–449.

(1087) Shan, X.; Li, J.; Chen, M.; Geske, T.; Bade, S. G. R.; Yu, Z. Junction Propagation in Organometal Halide Perovskite-Polymer Composite Thin Films. *J. Phys. Chem. Lett.* **2017**, *8*, 2412–2419.

(1088) Kim, S.; Bae, S.; Lee, S. W.; Cho, K.; Lee, K. D.; Kim, H.; Park, S.; Kwon, G.; Ahn, S. W.; Lee, H. M.; Kang, Y.; Lee, H. S.; Kim, D. Relationship Between Ion Migration and Interfacial Degradation of $\text{CH}_3\text{NH}_3\text{PbI}_3$ Perovskite Solar Cells under Thermal Conditions. *Sci. Rep.* **2017**, *7*, 1200.

(1089) Fakharuddin, A.; Shabbir, U.; Qiu, W.; Iqbal, T.; Sultan, M.; Heremans, P.; Schmidt-Mende, L. Inorganic and Layered Perovskites for Optoelectronic Devices. *Adv. Mater.* **2019**, *31*, 1807095.

(1090) Xu, B.; Wang, W.; Zhang, X.; Cao, W.; Wu, D.; Liu, S.; Dai, H.; Chen, S.; Wang, K.; Sun, X. Bright and Efficient Light-Emitting Diodes Based on MA/Cs Double Cation Perovskite Nanocrystals. *J. Mater. Chem. C* **2017**, *5*, 6123–6128.

(1091) Deng, W.; Xu, X.; Zhang, X.; Zhang, Y.; Jin, X.; Wang, L.; Lee, S.-T.; Jie, J. Organometal Halide Perovskite Quantum Dot Light-Emitting Diodes. *Adv. Funct. Mater.* **2016**, *26*, 4797–4802.

(1092) Yang, J. N.; Song, Y.; Yao, J. S.; Wang, K. H.; Wang, J. J.; Zhu, B. S.; Yao, M. M.; Rahman, S. U.; Lan, Y. F.; Fan, F. J.; Yao, H. B. Potassium Bromide Surface Passivation on $\text{CsPbI}_{3-x}\text{Br}_x$ Nanocrystals for Efficient and Stable Pure Red Perovskite Light-Emitting Diodes. *J. Am. Chem. Soc.* **2020**, *142*, 2956–2967.

(1093) Begum, R.; Chin, X. Y.; Damodaran, B.; Hooper, T. J. N.; Mhaisalkar, S.; Mathews, N. Cesium Lead Halide Perovskite Nanocrystals Prepared by Anion Exchange for Light-Emitting Diodes. *ACS Appl. Nano Mater.* **2020**, *3*, 1766–1774.

(1094) Chen, H.; Fan, L.; Zhang, R.; Bao, C.; Zhao, H.; Xiang, W.; Liu, W.; Niu, G.; Guo, R.; Zhang, L.; Wang, L. High-Efficiency Formamidinium Lead Bromide Perovskite Nanocrystal-Based Light-Emitting Diodes Fabricated via a Surface Defect Self-Passivation Strategy. *Adv. Opt. Mater.* **2020**, *8*, 1901390.

(1095) Hou, S.; Gangishetty, M. K.; Quan, Q.; Congreve, D. N. Efficient Blue and White Perovskite Light-Emitting Diodes *via* Manganese Doping. *Joule* **2018**, *2*, 2421–2433.

(1096) Yang, F.; Chen, H.; Zhang, R.; Liu, X.; Zhang, W.; Zhang, J.; Gao, F.; Wang, L. Efficient and Spectrally Stable Blue Perovskite Light-Emitting Diodes Based on Potassium Passivated Nanocrystals. *Adv. Funct. Mater.* **2020**, *30*, 1908760.

(1097) Hassan, Y.; Ashton, O. J.; Park, J. H.; Li, G.; Sakai, N.; Wenger, B.; Haghaghirad, A.-A.; Noel, N. K.; Song, M. H.; Lee, B. R.; Friend, R. H.; Snaith, H. J. Facile Synthesis of Stable and Highly Luminescent Methylammonium Lead Halide Nanocrystals for Efficient Light Emitting Devices. *J. Am. Chem. Soc.* **2019**, *141*, 1269–1279.

(1098) Zhang, X.; Sun, C.; Zhang, Y.; Wu, H.; Ji, C.; Chuai, Y.; Wang, P.; Wen, S.; Zhang, C.; Yu, W. W. Bright Perovskite Nanocrystal Films for Efficient Light-Emitting Devices. *J. Phys. Chem. Lett.* **2016**, *7*, 4602–4610.

(1099) Vashishtha, P.; Halpert, J. E. Field-Driven Ion Migration and Color Instability in Red-Emitting Mixed Halide Perovskite Nanocrystal Light-Emitting Diodes. *Chem. Mater.* **2017**, *29*, 5965–5973.

(1100) Zheng, X.; Yuan, S.; Liu, J.; Yin, J.; Yuan, F.; Shen, W.-S.; Yao, K.; Wei, M.; Zhou, C.; Song, K.; Zhang, B.-B.; Lin, Y.; Hedhili, M. N.; Wehbe, N.; Han, Y.; Sun, H.-T.; Lu, Z.-H.; Anthopoulos, T. D.; Mohammed, O. F.; Sargent, E. H.; Liao, L.-S.; Bakr, O. M. Chlorine Vacancy Passivation in Mixed Halide Perovskite Quantum Dots by Organic Pseudohalides Enables Efficient Rec. 2020 Blue Light-Emitting Diodes. *ACS Energy Lett.* **2020**, *5*, 793–798.

(1101) Dong, Y.; Wang, Y.-K.; Yuan, F.; Johnston, A.; Liu, Y.; Ma, D.; Choi, M.-J.; Chen, B.; Chekini, M.; Baek, S.-W.; Sagar, L. K.; Fan, J.; Hou, Y.; Wu, M.; Lee, S.; Sun, B.; Hoogland, S.; Quintero-Bermudez, R.; Ebe, H.; Todorovic, P.; et al. Bipolar-Shell Resurfacing for Blue LEDs Based on Strongly Confined Perovskite Quantum Dots. *Nat. Nanotechnol.* **2020**, *15*, 668–674.

(1102) Hoye, R. L. Z.; Lai, M.-L.; Anaya, M.; Tong, Y.; Galkowski, K.; Doherty, T.; Li, W.; Huq, T. N.; Mackowski, S.; Polavarapu, L.; Feldmann, J.; MacManus-Driscoll, J. L.; Friend, R. H.; Urban, A. S.; Stranks, S. D. Identifying and Reducing Interfacial Losses to Enhance Color-Pure Electroluminescence in Blue-Emitting Perovskite Nanoplatelet Light-Emitting Diodes. *ACS Energy Lett.* **2019**, *4*, 1181–1188.

(1103) Zhang, C.; Wan, Q.; Wang, B.; Zheng, W.; Liu, M.; Zhang, Q.; Kong, L.; Li, L. Surface Ligand Engineering toward Brightly Luminescent and Stable Cesium Lead Halide Perovskite Nanoplatelets for Efficient Blue-Light-Emitting Diodes. *J. Phys. Chem. C* **2019**, *123*, 26161–26169.

(1104) Chen, F.; Boopathi, K. M.; Imran, M.; Lauciello, S.; Salerno, M. Thiocyanate-Treated Perovskite-Nanocrystal-Based Light-Emitting Diodes with Insight in Efficiency Roll-Off. *Materials* **2020**, *13*, 367.

(1105) Brown, A. A. M.; Hooper, T. J. N.; Veldhuis, S. A.; Chin, X. Y.; Bruno, A.; Vashishtha, P.; Tey, J. N.; Jiang, L.; Damodaran, B.; Pu, S. H.; Mhaisalkar, S. G.; Mathews, N. Self-assembly of a Robust Hydrogen-Bonded Octylphosphonate Network on Cesium Lead Bromide Perovskite Nanocrystals for Light-Emitting Diodes. *Nanoscale* **2019**, *11*, 12370–12380.

(1106) Shynkarenko, Y.; Bodnarchuk, M. I.; Bernasconi, C.; Berezhovska, Y.; Verteletskyi, V.; Ochsenbein, S. T.; Kovalenko, M. V. Direct Synthesis of Quaternary Alkylammonium-Capped Perovskite Nanocrystals for Efficient Blue and Green Light-Emitting Diodes. *ACS Energy Lett.* **2019**, *4*, 2703–2711.

(1107) Song, J.; Li, J.; Xu, L.; Li, J.; Zhang, F.; Han, B.; Shan, Q.; Zeng, H. Room-Temperature Triple-Ligand Surface Engineering Synergistically Boosts Ink Stability, Recombination Dynamics, and Charge Injection toward EQE-11.6% Perovskite QLEDs. *Adv. Mater.* **2018**, *30*, 1800764.

(1108) Chen, H.; Fan, L.; Zhang, R.; Bao, C.; Zhao, H.; Xiang, W.; Liu, W.; Niu, G.; Guo, R.; Zhang, L.; Wang, L. High-Efficiency Formamidinium Lead Bromide Perovskite Nanocrystal-Based Light-Emitting Diodes Fabricated *via* a Surface Defect Self-Passivation Strategy. *Adv. Opt. Mater.* **2020**, *8*, 1901390.

(1109) Zheng, W.; Wan, Q.; Zhang, Q.; Liu, M.; Zhang, C.; Wang, B.; Kong, L.; Li, L. High-Efficiency Perovskite Nanocrystal Light-Emitting Diodes *via* Decorating NiO_x on the Nanocrystal Surface. *Nanoscale* **2020**, *12*, 8711–8719.

(1110) Bi, C.; Wang, S.; Li, Q.; Kershaw, S. V.; Tian, J.; Rogach, A. L. Thermally Stable Copper(II)-Doped Cesium Lead Halide Perovskite Quantum Dots with Strong Blue Emission. *J. Phys. Chem. Lett.* **2019**, *10*, 943–952.

(1111) Yu, D.; Cao, F.; Gao, Y.; Xiong, Y.; Zeng, H. Room-Temperature Ion-Exchange-Mediated Self-Assembly toward Formamidinium Perovskite Nanoplates with Finely Tunable, Ultrapure Green Emissions for Achieving Rec. 2020 Displays. *Adv. Funct. Mater.* **2018**, *28* (19), 1800248.

(1112) Congreve, D. N.; Weidman, M. C.; Seitz, M.; Paritmongkol, W.; Dahod, N. S.; Tisdale, W. A. Tunable Light-Emitting Diodes Utilizing Quantum-Confining Layered Perovskite Emitters. *ACS Photonics* **2017**, *4*, 476–481.

(1113) Jin, Y.; Wang, Z.-K.; Yuan, S.; Wang, Q.; Qin, C.; Wang, K.-L.; Dong, C.; Li, M.; Liu, Y.; Liao, L.-S. Synergistic Effect of Dual Ligands on Stable Blue Quasi-2D Perovskite Light-Emitting Diodes. *Adv. Funct. Mater.* **2020**, *30*, 1908339.

(1114) Lian, X.; Wang, X.; Ling, Y.; Lochner, E.; Tan, L.; Zhou, Y.; Ma, B.; Hanson, K.; Gao, H. Light Emitting Diodes Based on Inorganic Composite Halide Perovskites. *Adv. Funct. Mater.* **2018**, *29*, 1807345.

(1115) Shin, M.; Nam, S.-W.; Sadhanala, A.; Shivanna, R.; Anaya, M.; Jiménez-Solano, A.; Yoon, H.; Jeon, S.; Stranks, S. D.; Hoye, R. L. Z.; Shin, B. Understanding the Origin of Ultrasharp Sub-Bandgap Luminescence from Zero-Dimensional Inorganic Perovskite Cs_4PbBr_6 . *ACS Appl. Energy Mater.* **2020**, *3*, 192–199.

(1116) Ning, Z.; Gong, X.; Comin, R.; Walters, G.; Fan, F.; Voznyy, O.; Yassitepe, E.; Buin, A.; Hoogland, S.; Sargent, E. H. Quantum-Dot-in-Perovskite Solids. *Nature* **2015**, *523*, 324–328.

(1117) Gao, L.; Quan, L. N.; García de Arquer, F. P.; Zhao, Y.; Munir, R.; Proppe, A.; Quintero-Bermudez, R.; Zou, C.; Yang, Z.; Saidaminov, M. I.; Voznyy, O.; Kinge, S.; Lu, Z.; Kelley, S. O.; Amassian, A.; Tang, J.; Sargent, E. H. Efficient Near-Infrared Light-Emitting Diodes Based on Quantum Dots in Layered Perovskite. *Nat. Photonics* **2020**, *14*, 227–233.

(1118) Gong, X.; Yang, Z.; Walters, G.; Comin, R.; Ning, Z.; Beauregard, E.; Adinolfi, V.; Voznyy, O.; Sargent, E. H. Highly Efficient Quantum Dot Near-Infrared Light-Emitting Diodes. *Nat. Photonics* **2016**, *10*, 253–257.

(1119) Tong, J.; Wu, J.; Shen, W.; Zhang, Y.; Liu, Y.; Zhang, T.; Nie, S.; Deng, Z. Direct Hot-Injection Synthesis of Lead Halide Perovskite Nanocubes in Acrylic Monomers for Ultrastable and Bright Nanocrystal-Polymer Composite Films. *ACS Appl. Mater. Interfaces* **2019**, *11*, 9317–9325.

(1120) Li, G.; Tan, Z.-K.; Di, D.; Lai, M. L.; Jiang, L.; Lim, J. H.-W.; Friend, R. H.; Greenham, N. C. Efficient Light-Emitting Diodes Based on Nanocrystalline Perovskite in a Dielectric Polymer Matrix. *Nano Lett.* **2015**, *15*, 2640–2644.

(1121) Cai, W.; Chen, Z.; Li, Z.; Yan, L.; Zhang, D.; Liu, L.; Xu, Q.-h.; Ma, Y.; Huang, F.; Yip, H.-L.; Cao, Y. Polymer-Assisted *in Situ* Growth of All-Inorganic Perovskite Nanocrystal Film for Efficient and Stable Pure-Red Light-Emitting Devices. *ACS Appl. Mater. Interfaces* **2018**, *10*, 42564–42572.

(1122) Rainò, G.; Landuyt, A.; Krieg, F.; Bernasconi, C.; Ochsenbein, S. T.; Dirin, D. N.; Bodnarchuk, M. I.; Kovalenko, M. V. Underestimated Effect of a Polymer Matrix on the Light Emission of Single CsPbBr_3 Nanocrystals. *Nano Lett.* **2019**, *19*, 3648–3653.

(1123) Yoon, H. C.; Do, Y. R. Stable and Efficient Green Perovskite Nanocrystal-Polysilazane Films for White LEDs Using an Electrospray Deposition Process. *ACS Appl. Mater. Interfaces* **2019**, *11*, 22510–22520.

(1124) Hassan, Y.; Song, Y.; Pensack, R. D.; Abdelrahman, A. I.; Kobayashi, Y.; Winnik, M. A.; Scholes, G. D. Structure-Tuned Lead Halide Perovskite Nanocrystals. *Adv. Mater.* **2016**, *28*, 566–573.

(1125) Kumar, S.; Jagielski, J.; Marcato, T.; Solari, S. F.; Shih, C.-J. Understanding the Ligand Effects on Photophysical, Optical, and Electroluminescent Characteristics of Hybrid Lead Halide Perovskite Nanocrystal Solids. *J. Phys. Chem. Lett.* **2019**, *10*, 7560–7567.

(1126) Philippe, B.; Jacobsson, T. J.; Correa-Baena, J.-P.; Jena, N. K.; Banerjee, A.; Chakraborty, S.; Cappel, U. B.; Ahuja, R.; Hafeldt, A.; Odelius, M.; Rensmo, H. Valence Level Character in a Mixed Perovskite Material and Determination of the Valence Band Maximum from Photoelectron Spectroscopy: Variation with Photon Energy. *J. Phys. Chem. C* **2017**, *121*, 26655–26666.

(1127) Koscher, B. A.; Nett, Z.; Alivisatos, A. P. The Underlying Chemical Mechanism of Selective Chemical Etching in CsPbBr_3 Nanocrystals for Reliably Accessing Near-Unity Emitters. *ACS Nano* **2019**, *13*, 11825–11833.

(1128) Dai, S.-W.; Hsu, B.-W.; Chen, C.-Y.; Lee, C.-A.; Liu, H.-Y.; Wang, H.-F.; Huang, Y.-C.; Wu, T.-L.; Manikandan, A.; Ho, R.-M.; Tsao, C.-S.; Cheng, C.-H.; Chueh, Y.-L.; Lin, H.-W. Perovskite Quantum Dots with Near Unity Solution and Neat-Film Photoluminescent Quantum Yield by Novel Spray Synthesis. *Adv. Mater.* **2018**, *30*, 1705532.

(1129) Jagielski, J.; Kumar, S.; Wang, M.; Scullion, D.; Lawrence, R.; Li, Y.-T.; Yakunin, S.; Tian, T.; Kovalenko, M. V.; Chiu, Y.-C.; Santos, E. J. G.; Lin, S.; Shih, C.-J. Aggregation-Induced Emission in Lamellar Solids of Colloidal Perovskite Quantum Wells. *Sci. Adv.* **2017**, *3*, eaao0208.

(1130) Schuller, J. A.; Karaveli, S.; Schiros, T.; He, K.; Yang, S.; Kymmissis, I.; Shan, J.; Zia, R. Orientation of Luminescent Excitons in Layered Nanomaterials. *Nat. Nanotechnol.* **2013**, *8*, 271–276.

(1131) Jagielski, J.; Solari, S. F.; Jordan, L.; Scullion, D.; Blulle, B.; Li, Y. T.; Krumeich, F.; Chiu, Y. C.; Ruhstaller, B.; Santos, E. J. G.; Shih, C. J. Scalable Photonic Sources Using Two-Dimensional Lead Halide Perovskite Superlattices. *Nat. Commun.* **2020**, *11*, 387.

(1132) Zhang, B.-B.; Yuan, S.; Ma, J.-P.; Zhou, Y.; Hou, J.; Chen, X.; Zheng, W.; Shen, H.; Wang, X.-C.; Sun, B.; Bakr, O. M.; Liao, L.-S.; Sun, H.-T. General Mild Reaction Creates Highly Luminescent Organic-Ligand-Lacking Halide Perovskite Nanocrystals for Efficient Light-Emitting Diodes. *J. Am. Chem. Soc.* **2019**, *141*, 15423–15432.

(1133) Sim, K.; Jun, T.; Bang, J.; Kamioka, H.; Kim, J.; Hiramatsu, H.; Hosono, H. Performance Boosting Strategy for Perovskite Light-Emitting Diodes. *Appl. Phys. Rev.* **2019**, *6*, 031402.

(1134) Lu, M.; Guo, J.; Lu, P.; Zhang, L.; Zhang, Y.; Dai, Q.; Hu, Y.; Colvin, V. L.; Yu, W. W. Ammonium Thiocyanate-Passivated CsPbI_3 Perovskite Nanocrystals for Efficient Red Light-Emitting Diodes. *J. Phys. Chem. C* **2019**, *123*, 22787–22792.

(1135) Lignos, I.; Morad, V.; Shynkarenko, Y.; Bernasconi, C.; Maceiczyk, R. M.; Protesescu, L.; Bertolotti, F.; Kumar, S.; Ochsenbein, S. T.; Masciocchi, N.; Guagliardi, A.; Shih, C.-J.; Bodnarchuk, M. I.; deMello, A. J.; Kovalenko, M. V. Exploration of Near-Infrared-Emissive Colloidal Multinary Lead Halide Perovskite Nanocrystals Using an Automated Microfluidic Platform. *ACS Nano* **2018**, *12*, 5504–5517.

(1136) Solari, S. F.; Kumar, S.; Jagielski, J.; Shih, C.-J. Monochromatic LEDs Based on Perovskite Quantum Dots: Opportunities and Challenges. *J. Soc. Inf. Disp.* **2019**, *27*, 667–678.

(1137) Kumar, S.; Jagielski, J.; Tian, T.; Kallikounis, N.; Lee, W.-C.; Shih, C.-J. Mixing Entropy-Induced Layering Polydispersity Enabling Efficient and Stable Perovskite Nanocrystal Light-Emitting Diodes. *ACS Energy Lett.* **2019**, *4*, 118–125.

(1138) Chang, Y.-H.; Lin, J.-C.; Chen, Y.-C.; Kuo, T.-R.; Wang, D.-Y. Facile Synthesis of Two-Dimensional Ruddlesden–Popper Perovskite Quantum Dots with Fine-Tunable Optical Properties. *Nanoscale Res. Lett.* **2018**, *13*, 247.

(1139) Jagielski, J.; Kumar, S.; Yu, W.-Y.; Shih, C.-J. Layer-Controlled Two-Dimensional Perovskites: Synthesis and Optoelectronics. *J. Mater. Chem. C* **2017**, *5*, 5610–5627.

(1140) Richter, J. M.; Abdi-Jalebi, M.; Sadhanala, A.; Tabachnyk, M.; Rivett, J. P. H.; Pazos-Outón, L. M.; Gödel, K. C.; Price, M.; Deschler, F.; Friend, R. H. Enhancing Photoluminescence Yields in Lead Halide Perovskites by Photon Recycling and Light Out-Coupling. *Nat. Commun.* **2016**, *7*, 13941.

(1141) Xing, G.; Wu, B.; Wu, X.; Li, M.; Du, B.; Wei, Q.; Guo, J.; Yeow, E. K. L.; Sum, T. C.; Huang, W. Transcending the Slow Bimolecular Recombination in Lead-Halide Perovskites for Electroluminescence. *Nat. Commun.* **2017**, *8*, 14558.

(1142) Kim, Y.-H.; Wolf, C.; Kim, H.; Lee, T.-W. Charge Carrier Recombination and Ion Migration in Metal-Halide Perovskite Nanoparticle Films for Efficient Light-Emitting Diodes. *Nano Energy* **2018**, *52*, 329–335.

(1143) Kim, Y.-H.; Wolf, C.; Kim, Y.-T.; Cho, H.; Kwon, W.; Do, S.; Sadhanala, A.; Park, C. G.; Rhee, S.-W.; Im, S. H.; Friend, R. H.; Lee, T.-W. Highly Efficient Light-Emitting Diodes of Colloidal Metal-Halide Perovskite Nanocrystals beyond Quantum Size. *ACS Nano* **2017**, *11*, 6586–6593.

(1144) Hopper, T. R.; Gorodetsky, A.; Jeong, A.; Krieg, F.; Bodnarchuk, M. I.; Maimaris, M.; Chaplain, M.; Macdonald, T. J.; Huang, X.; Lovrincic, R.; Kovalenko, M. V.; Bakulin, A. A. Hot Carrier Dynamics in Perovskite Nanocrystal Solids: Role of the Cold Carriers, Nanoconfinement, and the Surface. *Nano Lett.* **2020**, *20*, 2271–2278.

(1145) Schaller, R. D.; Klimov, V. I. High Efficiency Carrier Multiplication in PbSe Nanocrystals: Implications for Solar Energy Conversion. *Phys. Rev. Lett.* **2004**, *92*, 186601.

(1146) Chen, J.; Messing, M. E.; Zheng, K.; Pullerits, T. Cation-Dependent Hot Carrier Cooling in Halide Perovskite Nanocrystals. *J. Am. Chem. Soc.* **2019**, *141*, 3532–3540.

(1147) Xu, H.; Wang, X.; Li, Y.; Cai, L.; Tan, Y.; Zhang, G.; Wang, Y.; Li, R.; Liang, D.; Song, T.; Sun, B. Prominent Heat Dissipation in Perovskite Light-Emitting Diodes with Reduced Efficiency Droop for Silicon-Based Display. *J. Phys. Chem. Lett.* **2020**, *11*, 3689–3698.

(1148) Wehrenfennig, C.; Liu, M.; Snaith, H. J.; Johnston, M. B.; Herz, L. M. Homogeneous Emission Line Broadening in the Organo Lead Halide Perovskite $\text{CH}_3\text{NH}_3\text{PbI}_{3-x}\text{Cl}_x$. *J. Phys. Chem. Lett.* **2014**, *5*, 1300–1306.

(1149) Naghadeh, S. B.; Sarang, S.; Brewer, A.; Allen, A. L.; Chiu, Y.-H.; Hsu, Y.-J.; Wu, J.-Y.; Ghosh, S.; Zhang, J. Z. Size and Temperature Dependence of Photoluminescence of Hybrid Perovskite Nanocrystals. *J. Chem. Phys.* **2019**, *151*, 154705.

(1150) Kim, Y.-H.; Cho, H.; Lee, T.-W. Metal Halide Perovskite Light Emitters. *Proc. Natl. Acad. Sci. U. S. A.* **2016**, *113*, 11694–11702.

(1151) Gan, J.; He, J.; Hoye, R. L. Z.; Mavlonov, A.; Raziq, F.; MacManus-Driscoll, J. L.; Wu, X.; Li, S.; Zu, X.; Zhan, Y.; Zhang, X.; Qiao, L. α - CsPbI_3 Colloidal Quantum Dots: Synthesis, Photodynamics, and Photovoltaic Applications. *ACS Energy Lett.* **2019**, *4*, 1308–1320.

(1152) Quan, L. N.; Rand, B. P.; Friend, R. H.; Mhaisalkar, S. G.; Lee, T.-W.; Sargent, E. H. Perovskites for Next-Generation Optical Sources. *Chem. Rev.* **2019**, *119*, 7444–7477.

(1153) Hoye, R. L. Z.; Chua, M. R.; Musselman, K. P.; Li, G.; Lai, M.-L.; Tan, Z.-K.; Greenham, N. C.; MacManus-Driscoll, J. L.; Friend, R. H.; Credgington, D. Enhanced Performance in Fluorene-Free Organometal Halide Perovskite Light-Emitting Diodes using Tunable, Low Electron Affinity Oxide Electron Injectors. *Adv. Mater.* **2015**, *27*, 1414–1419.

(1154) Qiu, W.; Hadipour, A.; Müller, R.; Conings, B.; Boyen, H.-G.; Heremans, P.; Froyen, L. Ultrathin Ammonium Heptamolybdate Films as Efficient Room-Temperature Hole Transport Layers for Organic Solar Cells. *ACS Appl. Mater. Interfaces* **2014**, *6*, 16335–16343.

(1155) Gangishetty, M. K.; Hou, S.; Quan, Q.; Congreve, D. N. Reducing Architecture Limitations for Efficient Blue Perovskite Light-Emitting Diodes. *Adv. Mater.* **2018**, *30*, 1706226.

(1156) Hoye, R. L. Z.; Musselman, K. P.; Chua, M. R.; Sadhanala, A.; Ranina, R. D.; MacManus-Driscoll, J. L.; Friend, R. H.; Credgington, D. Bright and Efficient Blue Polymer Light Emitting Diodes with Reduced Operating Voltages Processed Entirely at Low-Temperature. *J. Mater. Chem. C* **2015**, *3*, 9327–9336.

(1157) Endres, J.; Egger, D. A.; Kulbak, M.; Kerner, R. A.; Zhao, L.; Silver, S. H.; Hodes, G.; Rand, B. P.; Cahen, D.; Kronik, L.; Kahn, A. Valence and Conduction Band Densities of States of Metal Halide Perovskites: A Combined Experimental-Theoretical Study. *J. Phys. Chem. Lett.* **2016**, *7*, 2722–2729.

(1158) Zhang, F.; Silver, S. H.; Noel, N. K.; Ullrich, F.; Rand, B. P.; Kahn, A. Ultraviolet Photoemission Spectroscopy and Kelvin Probe Measurements on Metal Halide Perovskites: Advantages and Pitfalls. *Adv. Energy Mater.* **2020**, *10*, 1903252.

(1159) Tvingstedt, K.; Gil-Escrí, L.; Momblona, C.; Rieder, P.; Kiermasch, D.; Sessolo, M.; Baumann, A.; Bolink, H. J.; Dyakonov, V. Removing Leakage and Surface Recombination in Planar Perovskite Solar Cells. *ACS Energy Lett.* **2017**, *2*, 424–430.

(1160) Abdi-Jalebi, M.; Andaji-Garmaroudi, Z.; Cacovich, S.; Stavrakas, C.; Philippe, B.; Richter, J. M.; Alsari, M.; Booker, E. P.; Hutter, E. M.; Pearson, A. J.; Lilliu, S.; Savenije, T. J.; Rensmo, H.; Divitini, G.; Ducati, C.; Friend, R. H.; Stranks, S. D. Maximizing and Stabilizing Luminescence from Halide Perovskites with Potassium Passivation. *Nature* **2018**, *555*, 497–501.

(1161) Wang, L.; Moghe, D.; Hafezian, S.; Chen, P.; Young, M.; Elinski, M.; Martinu, L.; Kéna-Cohen, S.; Lunt, R. R. Alkali Metal Halide Salts as Interface Additives to Fabricate Hysteresis-Free Hybrid Perovskite-Based Photovoltaic Devices. *ACS Appl. Mater. Interfaces* **2016**, *8*, 23086–23094.

(1162) Jiang, Q.; Zhao, Y.; Zhang, X.; Yang, X.; Chen, Y.; Chu, Z.; Ye, Q.; Li, X.; Yin, Z.; You, J. Surface Passivation of Perovskite Film for Efficient Solar Cells. *Nat. Photonics* **2019**, *13*, 460–466.

(1163) Shi, Y.; Wu, W.; Dong, H.; Li, G.; Xi, K.; Divitini, G.; Ran, C.; Yuan, F.; Zhang, M.; Jiao, B.; Hou, X.; Wu, Z. A Strategy for Architecture Design of Crystalline Perovskite Light-Emitting Diodes with High Performance. *Adv. Mater.* **2018**, *30*, 1800251.

(1164) Snaith, H. J.; Abate, A.; Ball, J. M.; Eperon, G. E.; Leijtens, T.; Noel, N. K.; Stranks, S. D.; Wang, J. T.-W.; Wojciechowski, K.; Zhang, W. Anomalous Hysteresis in Perovskite Solar Cells. *J. Phys. Chem. Lett.* **2014**, *5*, 1511–1515.

(1165) van Reenen, S.; Kemerink, M.; Snaith, H. J. Modeling Anomalous Hysteresis in Perovskite Solar Cells. *J. Phys. Chem. Lett.* **2015**, *6*, 3808–3814.

(1166) Aygüler, M. F.; Weber, M. D.; Puscher, B. M. D.; Medina, D. D.; Docampo, P.; Costa, R. D. Light-Emitting Electrochemical Cells Based on Hybrid Lead Halide Perovskite Nanoparticles. *J. Phys. Chem. C* **2015**, *119*, 12047–12054.

(1167) Puscher, B. M. D.; Aygüler, M. F.; Docampo, P.; Costa, R. D. Unveiling the Dynamic Processes in Hybrid Lead Bromide Perovskite Nanoparticle Thin Film Devices. *Adv. Energy Mater.* **2017**, *7*, 1602283.

(1168) Cho, H.; Wolf, C.; Kim, J. S.; Yun, H. J.; Bae, J. S.; Kim, H.; Heo, J.-M.; Ahn, S.; Lee, T.-W. High-Efficiency Solution-Processed Inorganic Metal Halide Perovskite Light-Emitting Diodes. *Adv. Mater.* **2017**, *29*, 1700579.

(1169) Chen, M.; Shan, X.; Geske, T.; Li, J.; Yu, Z. Manipulating Ion Migration for Highly Stable Light-Emitting Diodes with Single-Crystalline Organometal Halide Perovskite Microplatelets. *ACS Nano* **2017**, *11*, 6312–6318.

(1170) Hoke, E. T.; Slotcavage, D. J.; Dohner, E. R.; Bowring, A. R.; Karunadasa, H. I.; McGehee, M. D. Reversible Photo-Induced Trap Formation in Mixed-Halide Hybrid Perovskites for Photovoltaics. *Chem. Sci.* **2015**, *6*, 613–617.

(1171) Zhang, H.; Fu, X.; Tang, Y.; Wang, H.; Zhang, C.; Yu, W. W.; Wang, X.; Zhang, Y.; Xiao, M. Phase Segregation due to Ion Migration in All-Inorganic Mixed-halide Perovskite Nanocrystals. *Nat. Commun.* **2019**, *10*, 1088.

(1172) Gualdrón-Reyes, A. F.; Yoon, S. J.; Barea, E. M.; Agouram, S.; Muñoz-Sanjosé, V.; Meléndez, Á. M.; Niño-Gómez, M. E.; Mora-Seró, I. Controlling the Phase Segregation in Mixed Halide Perovskites through Nanocrystal Size. *ACS Energy Lett.* **2019**, *4*, 54–62.

(1173) Wang, K.-H.; Peng, Y.; Ge, J.; Jiang, S.; Zhu, B.-S.; Yao, J.; Yin, Y.-C.; Yang, J.-N.; Zhang, Q.; Yao, H.-B. Efficient and Color-Tunable Quasi-2D $\text{CsPbBr}_x\text{Cl}_{3-x}$ Perovskite Blue Light-Emitting Diodes. *ACS Photonics* **2019**, *6*, 667–676.

(1174) Meloni, S.; Palermo, G.; Ashari-Astani, N.; Grätzel, M.; Rothlisberger, U. Valence and Conduction Band Tuning in Halide Perovskites for Solar Cell Applications. *J. Mater. Chem. A* **2016**, *4*, 15997–16002.

(1175) Ko, Y. H.; Jalalah, M.; Lee, S. J.; Park, J. G. Super Ultra-High Resolution Liquid-Crystal-Display Using Perovskite Quantum-Dot Functional Color-Filters. *Sci. Rep.* **2018**, *8*, 12881.

(1176) Yang, P.; Zhang, L.; Kang, D. J.; Strahl, R.; Kraus, T. High-Resolution Inkjet Printing of Quantum Dot Light-Emitting Microdiode Arrays. *Adv. Opt. Mater.* **2020**, *8*, 1901429.

(1177) Worku, M.; Tian, Y.; Zhou, C.; Lin, H.; Chaaban, M.; Xu, L. J.; He, Q.; Beery, D.; Zhou, Y.; Lin, X.; Su, Y. F.; Xin, Y.; Ma, B. Hollow Metal Halide Perovskite Nanocrystals with Efficient Blue Emissions. *Sci. Adv.* **2020**, *6*, eaaz5961.

(1178) Johnston, M. B.; Herz, L. M. Hybrid Perovskites for Photovoltaics: Charge-Carrier Recombination, Diffusion, and Radiative Efficiencies. *Acc. Chem. Res.* **2016**, *49*, 146–54.

(1179) Ambrosio, F.; Wiktor, J.; De Angelis, F.; Pasquarello, A. Origin of Low Electron-Hole Recombination Rate in Metal Halide Perovskites. *Energy Environ. Sci.* **2018**, *11*, 101–105.

(1180) Wolff, C. M.; Caprioglio, P.; Stolterfoht, M.; Neher, D. Nonradiative Recombination in Perovskite Solar Cells: The Role of Interfaces. *Adv. Mater.* **2019**, *31*, 1902762.

(1181) Yang, M.; Zeng, Y.; Li, Z.; Kim, D. H.; Jiang, C. S.; van de Lagemaat, J.; Zhu, K. Do Grain Boundaries Dominate Non-Radiative Recombination in $\text{CH}_3\text{NH}_3\text{PbI}_3$ Perovskite Thin Films? *Phys. Chem. Chem. Phys.* **2017**, *19*, 5043–5050.

(1182) Luo, D.; Su, R.; Zhang, W.; Gong, Q.; Zhu, R. Minimizing Non-Radiative Recombination Losses in Perovskite Solar Cells. *Nat. Rev. Mater.* **2020**, *5*, 44–60.

(1183) Zheng, K.; Zhu, Q.; Abdellah, M.; Messing, M. E.; Zhang, W.; Generalov, A.; Niu, Y.; Ribaud, L.; Canton, S. E.; Pullerits, T. Exciton Binding Energy and the Nature of Emissive States in Organometal Halide Perovskites. *J. Phys. Chem. Lett.* **2015**, *6*, 2969–75.

(1184) Lee, H. D.; Kim, H.; Cho, H.; Cha, W.; Hong, Y.; Kim, Y. H.; Sadhanala, A.; Venugopalan, V.; Kim, J. S.; Choi, J. W.; Lee, C. L.; Kim, D.; Yang, H.; Friend, R. H.; Lee, T. W. Efficient Ruddlesden–Popper Perovskite Light-Emitting Diodes with Randomly Oriented Nanocrystals. *Adv. Funct. Mater.* **2019**, *29*, 1901225.

(1185) Wang, K.; Wu, C.; Jiang, Y.; Yang, D.; Wang, K.; Priya, S. Distinct Conducting Layer Edge States in Two-Dimensional (2D) Halide Perovskite. *Sci. Adv.* **2019**, *5*, eaau3241.

(1186) Zheng, K.; Pullerits, T. Two Dimensions Are Better for Perovskites. *J. Phys. Chem. Lett.* **2019**, *10*, 5881–5885.

(1187) Yan, F.; Xing, J.; Xing, G.; Quan, L.; Tan, S. T.; Zhao, J.; Su, R.; Zhang, L.; Chen, S.; Zhao, Y.; Huan, A.; Sargent, E. H.; Xiong, Q.; Demir, H. V. Highly Efficient Visible Colloidal Lead-Halide Perovskite Nanocrystal Light-Emitting Diodes. *Nano Lett.* **2018**, *18*, 3157–3164.

(1188) Yang, X.; Zhang, X.; Deng, J.; Chu, Z.; Jiang, Q.; Meng, J.; Wang, P.; Zhang, L.; Yin, Z.; You, J. Efficient Green Light-Emitting Diodes Based on Quasi-Two-Dimensional Composition and Phase Engineered Perovskite with Surface Passivation. *Nat. Commun.* **2018**, *9*, 570.

(1189) Li, J.; Du, P.; Li, S.; Liu, J.; Zhu, M.; Tan, Z.; Hu, M.; Luo, J.; Guo, D.; Ma, L.; Nie, Z.; Ma, Y.; Gao, L.; Niu, G.; Tang, J. High-Throughput Combinatorial Optimizations of Perovskite Light-Emitting Diodes Based on All-Vacuum Deposition. *Adv. Funct. Mater.* **2019**, *29*, 1903607.

(1190) Hu, Y.; Wang, Q.; Shi, Y.-L.; Li, M.; Zhang, L.; Wang, Z.-K.; Liao, L.-S. Vacuum-Evaporated All-Inorganic Cesium Lead Bromine Perovskites for High-Performance Light-Emitting Diodes. *J. Mater. Chem. C* **2017**, *5*, 8144–8149.

(1191) Xie, S.; Osherov, A.; Bulović, V. All-Vacuum-Deposited Inorganic Cesium Lead Halide Perovskite Light-Emitting Diodes. *APL Mater.* **2020**, *8*, 051113.

(1192) Ni, Z.; Bao, C.; Liu, Y.; Jiang, Q.; Wu, W. Q.; Chen, S.; Dai, X.; Chen, B.; Hartweg, B.; Yu, Z.; Holman, Z.; Huang, J. Resolving Spatial and Energetic Distributions of Trap States in Metal Halide Perovskite Solar Cells. *Science* **2020**, *367*, 1352–1358.

(1193) Abbaszadeh, D.; Wetzelaer, G. A. H.; Nicolai, H. T.; Blom, P. W. M. Exciton Quenching at PEDOT:PSS Anode in Polymer Blue-Light-Emitting Diodes. *J. Appl. Phys.* **2014**, *116*, 224508.

(1194) Chen, Y.; Peng, J.; Su, D.; Chen, X.; Liang, Z. Efficient and Balanced Charge Transport Revealed in Planar Perovskite Solar Cells. *ACS Appl. Mater. Interfaces* **2015**, *7*, 4471–4475.

(1195) Shang, Y.; Liao, Y.; Wei, Q.; Wang, Z.; Xiang, B.; Ke, Y.; Liu, W.; Ning, Z. Highly Stable Hybrid Perovskite Light-Emitting Diodes Based on Dion-Jacobson Structure. *Sci. Adv.* **2019**, *5*, eaaw8072.

(1196) Yuan, Z.; Miao, Y.; Hu, Z.; Xu, W.; Kuang, C.; Pan, K.; Liu, P.; Lai, J.; Sun, B.; Wang, J.; Bai, S.; Gao, F. Unveiling the Synergistic Effect of Precursor Stoichiometry and Interfacial Reactions for Perovskite Light-Emitting Diodes. *Nat. Commun.* **2019**, *10*, 2818.

(1197) Zhang, L.; Yang, X.; Jiang, Q.; Wang, P.; Yin, Z.; Zhang, X.; Tan, H.; Yang, Y. M.; Wei, M.; Sutherland, B. R.; Sargent, E. H.; You, J. Ultra-Bright and Highly Efficient Inorganic Based Perovskite Light-Emitting Diodes. *Nat. Commun.* **2017**, *8*, 15640.

(1198) Whitaker, J. B.; Kim, D. H.; Larson, B. W.; Zhang, F.; Berry, J. J.; van Hest, M. F. A. M.; Zhu, K. Scalable Slot-Die Coating of High Performance Psolar Cells. *Sustain. Energy & Fuels* **2018**, *2*, 2442–2449.

(1199) Hoshi, K.; Chiba, T.; Sato, J.; Hayashi, Y.; Takahashi, Y.; Ebe, H.; Ohisa, S.; Kido, J. Purification of Perovskite Quantum Dots Using Low-Dielectric-Constant Washing Solvent "Diglyme" for Highly Efficient Light-Emitting Devices. *ACS Appl. Mater. Interfaces* **2018**, *10*, 24607–24612.

(1200) Hamill, J. C.; Schwartz, J.; Loo, Y.-L. Influence of Solvent Coordination on Hybrid Organic-Inorganic Perovskite Formation. *ACS Energy Lett.* **2018**, *3*, 92–97.

(1201) Adjokatse, S.; Fang, H.-H.; Loi, M. A. Broadly Tunable Metal Halide Perovskites for Solid-State Light-Emission Applications. *Mater. Today* **2017**, *20*, 413–424.

(1202) Xiao, P.; Huang, J.; Yan, D.; Luo, D.; Yuan, J.; Liu, B.; Liang, D. Emergence of Nanoplatelet Light-Emitting Diodes. *Materials* **2018**, *11*, 1376.

(1203) Stranks, S. D. Nonradiative Losses in Metal Halide Perovskites. *ACS Energy Lett.* **2017**, *2*, 1515–1525.

(1204) Zhang, Z. Y.; Wang, H. Y.; Zhang, Y. X.; Hao, Y. W.; Sun, C.; Zhang, Y.; Gao, B. R.; Chen, Q. D.; Sun, H. B. The Role of Trap-Assisted Recombination in Luminescent Properties of Organometal Halide $\text{CH}_3\text{NH}_3\text{PbBr}_3$ Perovskite Films and Quantum Dots. *Sci. Rep.* **2016**, *6*, 27286.

(1205) Mariano, F.; Creti, A.; Carbone, L.; Genco, A.; D'Agostino, S.; Carallo, S.; Montagna, G.; Lomascolo, M.; Mazzeo, M. The Enhancement of Excitonic Emission Crossing Saha Equilibrium in Trap Passivated $\text{CH}_3\text{NH}_3\text{PbBr}_3$ Perovskite. *Commun. Phys.* **2020**, *3*, 41.

(1206) Zou, W.; Li, R.; Zhang, S.; Liu, Y.; Wang, N.; Cao, Y.; Miao, Y.; Xu, M.; Guo, Q.; Di, D.; Zhang, L.; Yi, C.; Gao, F.; Friend, R. H.; Wang, J.; Huang, W. Minimising Efficiency Roll-Off in High-Brightness Perovskite Light-Emitting Diodes. *Nat. Commun.* **2018**, *9*, 608.

(1207) Wu, W.; Zhang, Y.; Liang, T.; Fan, J. Carrier Accumulation Enhanced Auger Recombination and Inner Self-Heating-Induced Spectrum Fluctuation in CsPbBr_3 Perovskite Nanocrystal Light-Emitting Devices. *Appl. Phys. Lett.* **2019**, *115*, 243503.

(1208) Jung, Y. J.; Cho, S. Y.; Jung, J. W.; Kim, S. Y.; Lee, J. H. Influence of Indium-Tin-Oxide and Emitting-Layer Thicknesses on Light Outcoupling of Perovskite Light-Emitting Diodes. *Nano Converg.* **2019**, *6*, 26.

(1209) Shen, Y.; Cheng, L. P.; Li, Y. Q.; Li, W.; Chen, J. D.; Lee, S. T.; Tang, J. X. High-Efficiency Perovskite Light-Emitting Diodes with Synergetic Outcoupling Enhancement. *Adv. Mater.* **2019**, *31*, 1901517.

(1210) Wu, T.; Ahmadi, M.; Hu, B. Giant Current Amplification Induced by Ion Migration in Perovskite Single Crystal Photodetectors. *J. Mater. Chem. C* **2018**, *6*, 8042–8050.

(1211) Dong, Q.; Lei, L.; Mendes, J.; So, F. Operational Stability of Perovskite Light Emitting Diodes. *J. Phys. Mater.* **2020**, *3*, 012002.

(1212) Xu, B.; Wang, W.; Zhang, X.; Liu, H.; Zhang, Y.; Mei, G.; Chen, S.; Wang, K.; Wang, L.; Sun, X. W. Electric Bias Induced Degradation in Organic-Inorganic Hybrid Perovskite Light-Emitting Diodes. *Sci. Rep.* **2018**, *8*, 15799.

(1213) Rivkin, B.; Fassl, P.; Sun, Q.; Taylor, A. D.; Chen, Z.; Vaynzof, Y. Effect of Ion Migration-Induced Electrode Degradation on the Operational Stability of Perovskite Solar Cells. *ACS Omega* **2018**, *3*, 10042–10047.

(1214) Adil Afroz, M.; Ghimire, N.; Reza, K. M.; Bahrami, B.; Bobba, R. S.; Gurung, A.; Chowdhury, A. H.; Iyer, P. K.; Qiao, Q. Thermal Stability and Performance Enhancement of Perovskite Solar Cells Through Oxalic Acid-Induced Perovskite Formation. *ACS Appl. Energy Mater.* **2020**, *3*, 2432–2439.

(1215) Heiderhoff, R.; Haeger, T.; Pourdavoud, N.; Hu, T.; Al-Khafaji, M.; Mayer, A.; Chen, Y.; Scheer, H.-C.; Riedl, T. Thermal Conductivity of Methylammonium Lead Halide Perovskite Single Crystals and Thin Films: A Comparative Study. *J. Phys. Chem. C* **2017**, *121*, 28306–28311.

(1216) Ge, C.; Hu, M.; Wu, P.; Tan, Q.; Chen, Z.; Wang, Y.; Shi, J.; Feng, J. Ultralow Thermal Conductivity and Ultrahigh Thermal Expansion of Single-Crystal Organic-Inorganic Hybrid Perovskite $\text{CH}_3\text{NH}_3\text{PbX}_3$ ($X = \text{Cl}, \text{Br}, \text{I}$). *J. Phys. Chem. C* **2018**, *122*, 15973–15978.

(1217) Gao, F.; Zhao, Y.; Zhang, X.; You, J. Recent Progresses on Defect Passivation toward Efficient Perovskite Solar Cells. *Adv. Energy Mater.* **2020**, *10*, 1902650.

(1218) Yuan, Y.; Wang, Q.; Shao, Y.; Lu, H.; Li, T.; Gruverman, A.; Huang, J. Electric-Field-Driven Reversible Conversion Between Methylammonium Lead Triiodide Perovskites and Lead Iodide at Elevated Temperatures. *Adv. Energy Mater.* **2016**, *6*, 1501803.

(1219) Wong, K. W.; Yip, H. L.; Luo, Y.; Wong, K. Y.; Lau, W. M.; Low, K. H.; Chow, H. F.; Gao, Z. Q.; Yeung, W. L.; Chang, C. C. Blocking Reactions Between Indium-Tin Oxide and Poly (3,4-Ethylene Dioxothiophene)-Poly(Styrene Sulphonate) with a Self-Assembly Monolayer. *Appl. Phys. Lett.* **2002**, *80*, 2788–2790.

(1220) Wang, H.; Kim, D. H. Perovskite-Based Photodetectors: Materials and Devices. *Chem. Soc. Rev.* **2017**, *46*, 5204–5236.

(1221) Ahmadi, M.; Wu, T.; Hu, B. A Review on Organic-Inorganic Halide Perovskite Photodetectors: Device Engineering and Fundamental Physics. *Adv. Mater.* **2017**, *29*, 1605242.

(1222) Jing, H.; Peng, R.; Ma, R.-M.; He, J.; Zhou, Y.; Yang, Z.; Li, C.-Y.; Liu, Y.; Guo, X.; Zhu, Y.; Wang, D.; Su, J.; Sun, C.; Bao, W.; Wang, M. Flexible Ultrathin Single-Crystalline Perovskite Photodetector. *Nano Lett.* **2020**, *20*, 7144–7151.

(1223) Hu, X.; Zhang, X. D.; Liang, L.; Bao, J.; Li, S.; Yang, W. L.; Xie, Y. High-Performance Flexible Broadband Photodetector Based on Organolead Halide Perovskite. *Adv. Funct. Mater.* **2014**, *24*, 7373–7380.

(1224) Xia, H. R.; Li, J.; Sun, W. T.; Peng, L. M. Organohalide Lead Perovskite Based Photodetectors with Much Enhanced Performance. *Chem. Commun.* **2014**, *50*, 13695–7.

(1225) Kwak, D.-H.; Lim, D.-H.; Ra, H.-S.; Ramasamy, P.; Lee, J.-S. High Performance Hybrid Graphene- $\text{CsPbBr}_{3-x}\text{I}_x$ Perovskite Nanocrystal Photodetector. *RSC Adv.* **2016**, *6*, 65252–65256.

(1226) Wang, Y.; Zhang, Y.; Lu, Y.; Xu, W.; Mu, H.; Chen, C.; Qiao, H.; Song, J.; Li, S.; Sun, B.; Cheng, Y.-B.; Bao, Q. Hybrid Graphene-Perovskite Phototransistors with Ultrahigh Responsivity and Gain. *Adv. Opt. Mater.* **2015**, *3*, 1389–1396.

(1227) Li, X.; Yu, D.; Chen, J.; Wang, Y.; Cao, F.; Wei, Y.; Wu, Y.; Wang, L.; Zhu, Y.; Sun, Z.; Ji, J.; Shen, Y.; Sun, H.; Zeng, H. Constructing Fast Carrier Tracks into Flexible Perovskite Photodetector to Greatly Improve Responsivity. *ACS Nano* **2017**, *11*, 2015–2023.

(1228) Horvath, E.; Spina, M.; Szekrenyes, Z.; Kamaras, K.; Gaal, R.; Gachet, D.; Forro, L. Nanowires of Methylammonium Lead Iodide ($\text{CH}_3\text{NH}_3\text{PbI}_3$) Prepared by Low Temperature Solution-Mediated Crystallization. *Nano Lett.* **2014**, *14*, 6761–6.

(1229) Gao, L.; Zeng, K.; Guo, J.; Ge, C.; Du, J.; Zhao, Y.; Chen, C.; Deng, H.; He, Y.; Song, H.; Niu, G.; Tang, J. Passivated Single-Crystalline $\text{CH}_3\text{NH}_3\text{PbI}_3$ Nanowire Photodetector with High Detectivity and Polarization Sensitivity. *Nano Lett.* **2016**, *16*, 7446–7454.

(1230) Deng, W.; Zhang, X.; Huang, L.; Xu, X.; Wang, L.; Wang, J.; Shang, Q.; Lee, S. T.; Jie, J. Aligned Single-Crystalline Perovskite Microwire Arrays for High-Performance Flexible Image Sensors with Long-Term Stability. *Adv. Mater.* **2016**, *28*, 2201–8.

(1231) Feng, J.; Yan, X.; Liu, Y.; Gao, H.; Wu, Y.; Su, B.; Jiang, L. Crystallographically Aligned Perovskite Structures for High-Performance Polarization-Sensitive Photodetectors. *Adv. Mater.* **2017**, *29*, 1605993.

(1232) Dai, Z.; Ou, Q.; Wang, C.; Si, G.; Shabbir, B.; Zheng, C.; Wang, Z.; Zhang, Y.; Huang, Y.; Dong, Y.; Jasieniak, J. J.; Su, B.; Bao, Q. Capillary-Bridge Mediated Assembly of Aligned Perovskite Quantum Dots for High-Performance Photodetectors. *J. Mater. Chem. C* **2019**, *7*, 5954–5961.

(1233) Tan, Z.; Wu, Y.; Hong, H.; Yin, J.; Zhang, J.; Lin, L.; Wang, M.; Sun, X.; Sun, L.; Huang, Y.; Liu, K.; Liu, Z.; Peng, H. Two-Dimensional $(\text{C}_4\text{H}_9\text{NH}_3)_2\text{PbBr}_4$ Perovskite Crystals for High-Performance Photodetector. *J. Am. Chem. Soc.* **2016**, *138*, 16612–16615.

(1234) Ou, Q.; Zhang, Y.; Wang, Z.; Yuwono, J. A.; Wang, R.; Dai, Z.; Li, W.; Zheng, C.; Xu, Z. Q.; Qi, X.; Duhm, S.; Medhekar, N. V.; Zhang, H.; Bao, Q. Strong Depletion in Hybrid Perovskite *p-n* Junctions Induced by Local Electronic Doping. *Adv. Mater.* **2018**, *30*, 1705792.

(1235) Feng, J.; Gong, C.; Gao, H.; Wen, W.; Gong, Y.; Jiang, X.; Zhang, B.; Wu, Y.; Wu, Y.; Fu, H.; Jiang, L.; Zhang, X. Single-Crystalline Layered Metal-Halide Perovskite Nanowires for Ultra-sensitive Photodetectors. *Nat. Electron.* **2018**, *1*, 404–410.

(1236) Cheng, H. C.; Wang, G.; Li, D.; He, Q.; Yin, A.; Liu, Y.; Wu, H.; Ding, M.; Huang, Y.; Duan, X. Van der Waals Heterojunction Devices Based on Organohalide Perovskites and Two-Dimensional Materials. *Nano Lett.* **2016**, *16*, 367–73.

(1237) Qi, X.; Zhang, Y.; Ou, Q.; Ha, S. T.; Qiu, C. W.; Zhang, H.; Cheng, Y. B.; Xiong, Q.; Bao, Q. Photonics and Optoelectronics of 2D Metal-Halide Perovskites. *Small* **2018**, *14*, 1800682.

(1238) Liu, J.; Xue, Y.; Wang, Z.; Xu, Z.-Q.; Zheng, C.; Weber, B.; Song, J.; Wang, Y.; Lu, Y.; Zhang, Y.; Bao, Q. Two-Dimensional $\text{CH}_3\text{NH}_3\text{PbI}_3$ Perovskite: Synthesis and Optoelectronic Application. *ACS Nano* **2016**, *10*, 3536–3542.

(1239) Kang, D. H.; Pae, S. R.; Shim, J.; Yoo, G.; Jeon, J.; Leem, J. W.; Yu, J. S.; Lee, S.; Shin, B.; Park, J. H. An Ultrahigh-Performance Photodetector based on a Perovskite-Transition-Metal-Dichalcogenide Hybrid Structure. *Adv. Mater.* **2016**, *28*, 7799–806.

(1240) Wehrenfennig, C.; Liu, M.; Snaith, H. J.; Johnston, M. B.; Herz, L. M. Charge-carrier Dynamics in Vapour-Deposited Films of the Organolead Halide Perovskite $\text{CH}_3\text{NH}_3\text{PbI}_{3-x}\text{Cl}_x$. *Energy Environ. Sci.* **2014**, *7*, 2269–2275.

(1241) Li, F.; Ma, C.; Wang, H.; Hu, W.; Yu, W.; Sheikh, A. D.; Wu, T. Ambipolar Solution-Processed Hybrid Perovskite Phototransistors. *Nat. Commun.* **2015**, *6*, 8238.

(1242) Ngai, J. H. L.; Ho, J. K. W.; Chan, R. K. H.; Cheung, S. H.; Leung, L. M.; So, S. K. Growth, Characterization, and Thin Film Transistor Application of $\text{CH}_3\text{NH}_3\text{PbI}_3$ Perovskite on Polymeric Gate Dielectric Layers. *RSC Adv.* **2017**, *7*, 49353–49360.

(1243) Zeidell, A. M.; Tyznik, C.; Jennings, L.; Zhang, C.; Lee, H.; Guthold, M.; Vardeny, Z. V.; Jurchescu, O. D. Enhanced Charge Transport in Hybrid Perovskite Field-Effect Transistors *via* Microstructure Control. *Adv. Electron. Mater.* **2018**, *4*, 1800316.

(1244) Ward, J. W.; Smith, H. L.; Zeidell, A.; Diemer, P. J.; Baker, S. R.; Lee, H.; Payne, M. M.; Anthony, J. E.; Guthold, M.; Jurchescu, O. D. Solution-Processed Organic and Halide Perovskite Transistors on Hydrophobic Surfaces. *ACS Appl. Mater. Interfaces* **2017**, *9*, 18120–18126.

(1245) Huo, C.; Liu, X.; Song, X.; Wang, Z.; Zeng, H. Field-Effect Transistors Based on Van-der-Waals-Grown and Dry-Transferred All-Inorganic Perovskite Ultrathin Platelets. *J. Phys. Chem. Lett.* **2017**, *8*, 4785–4792.

(1246) Yu, W.; Li, F.; Yu, L.; Niazi, M. R.; Zou, Y.; Corzo, D.; Basu, A.; Ma, C.; Dey, S.; Tietze, M. L.; Buttner, U.; Wang, X.; Wang, Z.; Hedhili, M. N.; Guo, C.; Wu, T.; Amassian, A. Single Crystal Hybrid Perovskite Field-Effect Transistors. *Nat. Commun.* **2018**, *9*, 5354.

(1247) Wang, Y.; Wan, Z.; Qian, Q.; Liu, Y.; Kang, Z.; Fan, Z.; Wang, P.; Wang, Y.; Li, C.; Jia, C.; Lin, Z.; Guo, J.; Shakir, I.; Goorsky, M.; Duan, X.; Zhang, Y.; Huang, Y.; Duan, X. Probing Photoelectrical Transport in Lead Halide Perovskites with Van der Waals Contacts. *Nat. Nanotechnol.* **2020**, *15*, 768–775.

(1248) Wang, G.; Li, D.; Cheng, H.-C.; Li, Y.; Chen, C.-Y.; Yin, A.; Zhao, Z.; Lin, Z.; Wu, H.; He, Q.; Ding, M.; Liu, Y.; Huang, Y.; Duan, X. Wafer-Scale Growth of Large Arrays of Perovskite Microplate Crystals for Functional Electronics and Optoelectronics. *Sci. Adv.* **2015**, *1*, e1500613.

(1249) Li, D.; Cheng, H. C.; Wang, Y.; Zhao, Z.; Wang, G.; Wu, H.; He, Q.; Huang, Y.; Duan, X. The Effect of Thermal Annealing on Charge Transport in Organolead Halide Perovskite Microplate Field-Effect Transistors. *Adv. Mater.* **2017**, *29*, 1601959.

(1250) Liang, Y.; Li, F.; Zheng, R. Low-Dimensional Hybrid Perovskites for Field-Effect Transistors with Improved Stability: Progress and Challenges. *Adv. Electron. Mater.* **2020**, *6*, 2000137.

(1251) Sytnyk, M.; Deumel, S.; Tedde, S. F.; Matt, G. J.; Heiss, W. A Perspective on the Bright Future of Metal Halide Perovskites for X-Ray Detection. *Appl. Phys. Lett.* **2019**, *115*, 190501.

(1252) Heo, J. H.; Shin, D. H.; Park, J. K.; Kim, D. H.; Lee, S. J.; Im, S. H. High-Performance Next-Generation Perovskite Nanocrystal Scintillator for Nondestructive X-Ray Imaging. *Adv. Mater.* **2018**, *30*, 1801743.

(1253) Pan, W.; Yang, B.; Niu, G.; Xue, K. H.; Du, X.; Yin, L.; Zhang, M.; Wu, H.; Miao, X. S.; Tang, J. Hot-Pressed CsPbBr_3 Quasi-Monocrystalline Film for Sensitive Direct X-ray Detection. *Adv. Mater.* **2019**, *31*, 1904405.

(1254) Yakunin, S.; Dirin, D. N.; Shynkarenko, Y.; Morad, V.; Cherniukh, I.; Nazarenko, O.; Kreil, D.; Nauser, T.; Kovalenko, M. V. Detection of Gamma Photons using Solution-Grown Single Crystals of Hybrid Lead Halide Perovskites. *Nat. Photonics* **2016**, *10*, 585–589.

(1255) Wei, H.; Huang, J. Halide Lead Perovskites for Ionizing Radiation Detection. *Nat. Commun.* **2019**, *10*, 1066.

(1256) Stoumpos, C. C.; Malliakas, C. D.; Peters, J. A.; Liu, Z.; Sebastian, M.; Im, J.; Chasapis, T. C.; Wibowo, A. C.; Chung, D. Y.; Freeman, A. J.; Wessels, B. W.; Kanatzidis, M. G. Crystal Growth of the Perovskite Semiconductor CsPbBr_3 : A New Material for High-Energy Radiation Detection. *Cryst. Growth Des.* **2013**, *13*, 2722–2727.

(1257) Wei, H.; Fang, Y.; Mulligan, P.; Chuirazzi, W.; Fang, H.-H.; Wang, C.; Ecker, B. R.; Gao, Y.; Loi, M. A.; Cao, L.; Huang, J. Sensitive X-Ray Detectors made of Methylammonium Lead Tribromide Perovskite Single Crystals. *Nat. Photonics* **2016**, *10*, 333–339.

(1258) Liu, J.; Shabbir, B.; Wang, C.; Wan, T.; Ou, Q.; Yu, P.; Tadich, A.; Jiao, X.; Chu, D.; Qi, D.; Li, D.; Kan, R.; Huang, Y.; Dong, Y.; Jasieniak, J.; Zhang, Y.; Bao, Q. Flexible, Printable Soft-X-Ray Detectors Based on All-Inorganic Perovskite Quantum Dots. *Adv. Mater.* **2019**, *31*, 1901644.

(1259) Chen, Q.; Wu, J.; Ou, X.; Huang, B.; Almutlaq, J.; Zhumekenov, A. A.; Guan, X.; Han, S.; Liang, L.; Yi, Z.; Li, J.; Xie, X.; Wang, Y.; Li, Y.; Fan, D.; Teh, D. B. L.; All, A. H.; Mohammed, O. F.; Bakr, O. M.; Wu, T.; et al. All-inorganic Perovskite Nanocrystal Scintillators. *Nature* **2018**, *561*, 88–93.

(1260) Yakunin, S.; Sytnyk, M.; Kriegner, D.; Shrestha, S.; Richter, M.; Matt, G. J.; Azimi, H.; Brabec, C. J.; Stangl, J.; Kovalenko, M. V.; Heiss, W. Detection of X-Ray Photons by Solution-Processed Organic-Inorganic Perovskites. *Nat. Photonics* **2015**, *9*, 444–449.

(1261) Wei, W.; Zhang, Y.; Xu, Q.; Wei, H.; Fang, Y.; Wang, Q.; Deng, Y.; Li, T.; Gruverman, A.; Cao, L.; Huang, J. Monolithic Integration of Hybrid Perovskite Single Crystals with Heterogenous Substrate for Highly Sensitive X-Ray Imaging. *Nat. Photonics* **2017**, *11*, 315–321.

(1262) Kim, Y. C.; Kim, K. H.; Son, D. Y.; Jeong, D. N.; Seo, J. Y.; Choi, Y. S.; Han, I. T.; Lee, S. Y.; Park, N. G. Printable Organometallic Perovskite Enables Large-Area, Low-Dose X-Ray Imaging. *Nature* **2017**, *550*, 87–91.

(1263) Maddalena, F.; Tjahjana, L.; Xie, A.; Arramel; Zeng, S.; Wang, H.; Coquet, P.; Dzordzowski, W.; Dujardin, C.; Dang, C.; Birowosuto, M. Inorganic, Organic, and Perovskite Halides with Nanotechnology for High-Light Yield X- and γ -Ray Scintillators. *Crystals* **2019**, *9*, 88.

(1264) Gandini, M.; Villa, I.; Beretta, M.; Gotti, C.; Imran, M.; Carulli, F.; Fantuzzi, E.; Sassi, M.; Zaffalon, M.; Brofferio, C.; Manna, L.; Beverina, L.; Vedda, A.; Fasoli, M.; Gironi, L.; Brovelli, S. Efficient, Fast and Reabsorption-Free Perovskite Nanocrystal-Based Sensitized Plastic Scintillators. *Nat. Nanotechnol.* **2020**, *15*, 462–468.

(1265) Cao, J.; Guo, Z.; Zhu, S.; Fu, Y.; Zhang, H.; Wang, Q.; Gu, Z. Preparation of Lead-free Two-Dimensional-Layered $(C_8H_{17}NH_3)_2SnBr_4$ Perovskite Scintillators and Their Application in X-Ray Imaging. *ACS Appl. Mater. Interfaces* **2020**, *12*, 19797–19804.

(1266) Zhu, W.; Ma, W.; Su, Y.; Chen, Z.; Chen, X.; Ma, Y.; Bai, L.; Xiao, W.; Liu, T.; Zhu, H.; Liu, X.; Liu, H.; Liu, X.; Yang, Y. Low-Dose Real-Time X-Ray Imaging with Nontoxic Double Perovskite Scintillators. *Light: Sci. Appl.* **2020**, *9*, 112.

(1267) Wang, A.; Jin, Z.; Cheng, M.; Hao, F.; Ding, L. Advances in Perovskite Quantum-Dot Solar Cells. *J. Energy Chem.* **2021**, *S2*, 351–353.

(1268) Yao, H.; Zhou, F.; Li, Z.; Ci, Z.; Ding, L.; Jin, Z. Strategies for Improving the Stability of Tin-Based Perovskite ($ASnX_3$) Solar Cells. *Adv. Sci.* **2020**, *7*, 1903540.

(1269) Hao, M.; Bai, Y.; Zeiske, S.; Ren, L.; Liu, J.; Yuan, Y.; Zarrabi, N.; Cheng, N.; Ghasemi, M.; Chen, P.; Lyu, M.; He, D.; Yun, J.-H.; Du, Y.; Wang, Y.; Ding, S.; Armin, A.; Meredith, P.; Liu, G.; Cheng, H.-M.; Wang, L. Ligand-Assisted Cation-Exchange Engineering for High-Efficiency Colloidal $Cs_{1-x}FA_xPbI_3$ Quantum Dot Solar Cells with Reduced Phase Segregation. *Nat. Energy* **2020**, *S*, 79–88.

(1270) Liu, C.; Zeng, Q.; Zhao, Y.; Yu, Y.; Yang, M.; Gao, H.; Wei, H.; Yang, B. Surface Ligands Management for Efficient $CsPbBrI_2$ Perovskite Nanocrystal Solar Cells. *Solar RRL* **2020**, *4*, 2000102.

(1271) Khan, J.; Zhang, X.; Yuan, J.; Wang, Y.; Shi, G.; Patterson, R.; Shi, J.; Ling, X.; Hu, L.; Wu, T.; Dai, S.; Ma, W. Tuning the Surface-Passivating Ligand Anchoring Position Enables Phase Robustness in $CsPbI_3$ Perovskite Quantum Dot Solar Cells. *ACS Energy Lett.* **2020**, *S*, 3322–3329.

(1272) Alivisatos, A. P. Semiconductor Clusters, Nanocrystals, and Quantum Dots. *Science* **1996**, *271*, 933–937.

(1273) Zhao, Q.; Hazarika, A.; Schelhas, L. T.; Liu, J.; Gaulding, E. A.; Li, G.; Zhang, M.; Toney, M. F.; Sercel, P. C.; Luther, J. M. Size-Dependent Lattice Structure and Confinement Properties in $CsPbI_3$ Perovskite Nanocrystals: Negative Surface Energy for Stabilization. *ACS Energy Lett.* **2020**, *S*, 238–247.

(1274) Shockley, W.; Queisser, H. J. Detailed Balance Limit of Efficiency of *p-n* Junction Solar Cells. *J. Appl. Phys.* **1961**, *32*, 510–519.

(1275) Gholipour, S.; Ali, A. M.; Correa-Baena, J.-P.; Turren-Cruz, S.-H.; Tajabadi, F.; Tress, W.; Taghavinia, N.; Grätzel, M.; Abate, A.; De Angelis, F.; Gaglioli, C. A.; Mosconi, E.; Hagfeldt, A.; Saliba, M. Globularity-Selected Large Molecules for a New Generation of Multication Perovskites. *Adv. Mater.* **2017**, *29*, 1702005.

(1276) Koh, T. M.; Fu, K.; Fang, Y.; Chen, S.; Sum, T. C.; Mathews, N.; Mhaisalkar, S. G.; Boix, P. P.; Baikie, T. Formamidinium-Containing Metal-Halide: An Alternative Material for Near-IR Absorption Perovskite Solar Cells. *J. Phys. Chem. C* **2014**, *118*, 16458–16462.

(1277) Kong, X.; Shayan, K.; Hua, S.; Strauf, S.; Lee, S. S. Complete Suppression of Detrimental Polymorph Transitions in All-Inorganic Perovskites *via* Nanoconfinement. *ACS Appl. Energy Mater.* **2019**, *2*, 2948–2955.

(1278) Masi, S.; Gualdrón Reyes, A. F.; Mora-Seró, I. Stabilization of Black Perovskite Phase in $FAPbI_3$ and $CsPbI_3$. *ACS Energy Lett.* **2020**, *S*, 1974–1985.

(1279) Sidhik, S.; Esparza, D.; Martínez-Benítez, A.; Lopez-Luke, T.; Carriles, R.; Mora-Seró, I.; de la Rosa, E. Enhanced Photovoltaic Performance of Mesoscopic Perovskite Solar Cells by Controlling the Interaction between $CH_3NH_3PbI_3$ Films and $CsPbX_3$ Perovskite Nanoparticles. *J. Phys. Chem. C* **2017**, *121*, 4239–4245.

(1280) Vigil, J. A.; Hazarika, A.; Luther, J. M.; Toney, M. F. $FA_xCs_{1-x}PbI_3$ Nanocrystals: Tuning Crystal Symmetry by A-Site Cation Composition. *ACS Energy Lett.* **2020**, *S*, 2475–2482.

(1281) Sanehira, E. M.; Marshall, A. R.; Christians, J. A.; Harvey, S. P.; Ciesielski, P. N.; Wheeler, L. M.; Schulz, P.; Lin, L. Y.; Beard, M. C.; Luther, J. M. Enhanced Mobility $CsPbI_3$ Quantum Dot Arrays for Record-Efficiency, High-Voltage Photovoltaic Cells. *Sci. Adv.* **2017**, *3*, eaao4204.

(1282) Wheeler, L. M.; Sanehira, E. M.; Marshall, A. R.; Schulz, P.; Suri, M.; Anderson, N. C.; Christians, J. A.; Nordlund, D.; Sokaras, D.; Kroll, T.; Harvey, S. P.; Berry, J. J.; Lin, L. Y.; Luther, J. M. Targeted Ligand-Exchange Chemistry on Cesium Lead Halide Perovskite Quantum Dots for High-Efficiency Photovoltaics. *J. Am. Chem. Soc.* **2018**, *140*, 10504–10513.

(1283) Li, F.; Zhou, S.; Yuan, J.; Qin, C.; Yang, Y.; Shi, J.; Ling, X.; Li, Y.; Ma, W. Perovskite Quantum Dot Solar Cells with 15.6% Efficiency and Improved Stability Enabled by an α - $CsPbI_3$ / $FAPbI_3$ Bilayer Structure. *ACS Energy Lett.* **2019**, *4*, 2571–2578.

(1284) Carey, G. H.; Abdelhady, A. L.; Ning, Z.; Thon, S. M.; Bakr, O. M.; Sargent, E. H. Colloidal Quantum Dot Solar Cells. *Chem. Rev.* **2015**, *115*, 12732–12763.

(1285) Owen, J.; Brus, L. Chemical Synthesis and Luminescence Applications of Colloidal Semiconductor Quantum Dots. *J. Am. Chem. Soc.* **2017**, *139*, 10939–10943.

(1286) Cardenas-Morcoso, D.; Gualdrón-Reyes, A. F.; Ferreira Vitoreti, A. B.; García-Tecedor, M.; Yoon, S. J.; Solis de la Fuente, M.; Mora-Seró, I.; Giménez, S. Photocatalytic and Photoelectrochemical Degradation of Organic Compounds with All-Inorganic Metal Halide Perovskite Quantum Dots. *J. Phys. Chem. Lett.* **2019**, *10*, 630–636.

(1287) Tress, W.; Marinova, N.; Inganäs, O.; Nazeeruddin, M. K.; Zakeeruddin, S. M.; Graetzel, M. Predicting the Open-Circuit Voltage of $CH_3NH_3PbI_3$ Perovskite Solar Cells Using Electroluminescence and Photovoltaic Quantum Efficiency Spectra: the Role of Radiative and Non-Radiative Recombination. *Adv. Energy Mater.* **2015**, *S*, 1400812.

(1288) Yuan, J.; Ling, X.; Yang, D.; Li, F.; Zhou, S.; Shi, J.; Qian, Y.; Hu, J.; Sun, Y.; Yang, Y.; Gao, X.; Duhm, S.; Zhang, Q.; Ma, W. Band-Aligned Polymeric Hole Transport Materials for Extremely Low Energy Loss α - $CsPbI_3$ Perovskite Nanocrystal Solar Cells. *Joule* **2018**, *2*, 2450–2463.

(1289) Christodoulou, S.; Di Stasio, F.; Pradhan, S.; Stavrinadis, A.; Konstantatos, G. High-Open-Circuit-Voltage Solar Cells Based on Bright Mixed-Halide $CsPbBrI_2$ Perovskite Nanocrystals Synthesized under Ambient Air Conditions. *J. Phys. Chem. C* **2018**, *122*, 7621–7626.

(1290) Akkerman, Q. A.; Gandini, M.; Di Stasio, F.; Rastogi, P.; Palazon, F.; Bertoni, G.; Ball, J. M.; Prato, M.; Petrozza, A.; Manna, L. Strongly Emissive Perovskite Nanocrystal Inks for High-Voltage Solar Cells. *Nat. Energy* **2017**, *2*, 16194.

(1291) Lin, Q.; Yun, H. J.; Liu, W.; Song, H.-J.; Makarov, N. S.; Isaienko, O.; Nakotte, T.; Chen, G.; Luo, H.; Klimov, V. I.; Pietryga, J. M. Phase-Transfer Ligand Exchange of Lead Chalcogenide Quantum Dots for Direct Deposition of Thick, Highly Conductive Films. *J. Am. Chem. Soc.* **2017**, *139*, 6644–6653.

(1292) Shrestha, A.; Batmunkh, M.; Tricoli, A.; Qiao, S. Z.; Dai, S. Near-Infrared Active Lead Chalcogenide Quantum Dots: Preparation, Post-Synthesis Ligand Exchange, and Applications in Solar Cells. *Angew. Chem., Int. Ed.* **2019**, *58*, 5202–5224.

(1293) Xu, Y.-F.; Wang, X.-D.; Liao, J.-F.; Chen, B.-X.; Chen, H.-Y.; Kuang, D.-B. Amorphous-TiO₂-Encapsulated CsPbBr₃ Nanocrystal Composite Photocatalyst with Enhanced Charge Separation and CO₂ Fixation. *Adv. Mater. Interfaces* **2018**, *5*, 1801015.

(1294) Zhao, Q.; Hazarika, A.; Chen, X.; Harvey, S. P.; Larson, B. W.; Teeter, G. R.; Liu, J.; Song, T.; Xiao, C.; Shaw, L.; Zhang, M.; Li, G.; Beard, M. C.; Luther, J. M. High Efficiency Perovskite Quantum Dot Solar Cells with Charge Separating Heterostructure. *Nat. Commun.* **2019**, *10*, 2842.

(1295) Hazarika, A.; Zhao, Q.; Gaulding, E. A.; Christians, J. A.; Dou, B.; Marshall, A. R.; Moot, T.; Berry, J. J.; Johnson, J. C.; Luther, J. M. Perovskite Quantum Dot Photovoltaic Materials beyond the Reach of Thin Films: Full-Range Tuning of A-Site Cation Composition. *ACS Nano* **2018**, *12*, 10327–10337.

(1296) Suarez, B.; Gonzalez-Pedro, V.; Ripolles, T. S.; Sanchez, R. S.; Otero, L.; Mora-Sero, I. Recombination Study of Combined Halides (Cl, Br, I) Perovskite Solar Cells. *J. Phys. Chem. Lett.* **2014**, *5*, 1628–1635.

(1297) Gualdrón-Reyes, A. F.; Yoon, S. J.; Mora-Seró, I. Recent Insights for Achieving Mixed Halide Perovskites without Halide Segregation. *Curr. Opin. Electrochem.* **2018**, *11*, 84–90.

(1298) Unger, E. L.; Kegelmann, L.; Suchan, K.; Sorell, D.; Korte, L.; Albrecht, S. Roadmap and Roadblocks for the Band Gap Tunability of Metal Halide Perovskites. *J. Mater. Chem. A* **2017**, *5*, 11401–11409.

(1299) Braly, I. L.; Stoddard, R. J.; Rajagopal, A.; Uhl, A. R.; Katahara, J. K.; Jen, A. K. Y.; Hillhouse, H. W. Current-Induced Phase Segregation in Mixed Halide Hybrid Perovskites and its Impact on Two-Terminal Tandem Solar Cell Design. *ACS Energy Lett.* **2017**, *2*, 1841–1847.

(1300) Draguta, S.; Sharia, O.; Yoon, S. J.; Brennan, M. C.; Morozov, Y. V.; Manser, J. S.; Kamat, P. V.; Schneider, W. F.; Kuno, M. Rationalizing the Light-induced Phase Separation of Mixed Halide Organic-Inorganic Perovskites. *Nat. Commun.* **2017**, *8*, 200.

(1301) Zolfaghari, Z.; Hassanabadi, E.; Pitarch-Tena, D.; Yoon, S. J.; Shariatinia, Z.; van de Lagemaat, J.; Luther, J. M.; Mora-Seró, I. Operation Mechanism of Perovskite Quantum Dot Solar Cells Probed by Impedance Spectroscopy. *ACS Energy Lett.* **2019**, *4*, 251–258.

(1302) Que, M.; Dai, Z.; Yang, H.; Zhu, H.; Zong, Y.; Que, W.; Padture, N. P.; Zhou, Y.; Chen, O. Quantum-Dot-Induced Cesium-Rich Surface Imparts Enhanced Stability to Formamidinium Lead Iodide Perovskite Solar Cells. *ACS Energy Lett.* **2019**, *4*, 1970–1975.

(1303) Liu, C.; Hu, M.; Zhou, X.; Wu, J.; Zhang, L.; Kong, W.; Li, X.; Zhao, X.; Dai, S.; Xu, B.; Cheng, C. Efficiency and Stability Enhancement of Perovskite Solar Cells by Introducing CsPbI₃ Quantum Dots as an Interface Engineering Layer. *NPG Asia Mater.* **2018**, *10*, 552–561.

(1304) Siddiqui, H. Lead-Free Perovskite Quantum Structures towards the Efficient Solar Cell. *Mater. Lett.* **2019**, *249*, 99–103.

(1305) Ke, W.; Kanatzidis, M. G. Prospects for Low-Toxicity Lead-Free Perovskite Solar Cells. *Nat. Commun.* **2019**, *10*, 965.

(1306) Jokar, E.; Chien, C.-H.; Tsai, C.-M.; Fathi, A.; Diau, E. W.-G. Robust Tin-Based Perovskite Solar Cells with Hybrid Organic Cations to Attain Efficiency Approaching 10%. *Adv. Mater.* **2019**, *31*, 1804835.

(1307) Xu, H.; Yuan, H.; Duan, J.; Zhao, Y.; Jiao, Z.; Tang, Q. Lead-Free CH₃NH₃SnBr_{3-x}I_x Perovskite Quantum Dots for Mesoscopic Solar Cell Applications. *Electrochim. Acta* **2018**, *282*, 807–812.

(1308) Hasan, S. A. U.; Lee, D. S.; Im, S. H.; Hong, K.-H. Present Status and Research Prospects of Tin-based Perovskite Solar Cells. *Solar RRL* **2020**, *4*, 1900310.

(1309) Xiao, Z.; Song, Z.; Yan, Y. From Lead Halide Perovskites to Lead-Free Metal Halide Perovskites and Perovskite Derivatives. *Adv. Mater.* **2019**, *31*, 1803792.

(1310) Zhou, L.; Liao, J.-F.; Huang, Z.-G.; Wang, X.-D.; Xu, Y.-F.; Chen, H.-Y.; Kuang, D.-B.; Su, C.-Y. All-Inorganic Lead-Free Cs₂PdX₆ (X = Br, I) Perovskite Nanocrystals with Single Unit Cell Thickness and High Stability. *ACS Energy Lett.* **2018**, *3*, 2613–2619.

(1311) Cho, J.; DuBose, J. T.; Kamat, P. V. Charge Injection from Excited Cs₂AgBiBr₆ Quantum Dots into Semiconductor Oxides. *Chem. Mater.* **2020**, *32*, 510–517.

(1312) Kung, P.-K.; Li, M.-H.; Lin, P.-Y.; Jhang, J.-Y.; Pantaler, M.; Lupascu, D. C.; Grancini, G.; Chen, P. Lead-Free Double Perovskites for Perovskite Solar Cells. *Solar RRL* **2020**, *4*, 1900306.

(1313) Funabiki, F.; Toda, Y.; Hosono, H. Optical and Electrical Properties of Perovskite Variant (CH₃NH₃)₂SnI₆. *J. Phys. Chem. C* **2018**, *122*, 10749–10754.

(1314) Chen, M.; Ju, M.-G.; Carl, A. D.; Zong, Y.; Grimm, R. L.; Gu, J.; Zeng, X. C.; Zhou, Y.; Padture, N. P. Cesium Titanium(IV) Bromide Thin Films Based Stable Lead-free Perovskite Solar Cells. *Joule* **2018**, *2*, 558–570.

(1315) Wu, C.; Zhang, Q.; Liu, Y.; Luo, W.; Guo, X.; Huang, Z.; Ting, H.; Sun, W.; Zhong, X.; Wei, S.; Wang, S.; Chen, Z.; Xiao, L. The Dawn of Lead-Free Perovskite Solar Cell: Highly Stable Double Perovskite Cs₂AgBiBr₆ Film. *Adv. Sci.* **2018**, *5*, 1700759.

(1316) Wali, Q.; Iftikhar, F. J.; Khan, M. E.; Ullah, A.; Iqbal, Y.; Jose, R. Advances in Stability of Perovskite Solar Cells. *Org. Electron.* **2020**, *78*, 105590.

(1317) Sidhik, S.; Rosiles Pérez, C.; Serrano Estrada, M. A.; López-Luke, T.; Torres, A.; De la Rosa, E. Improving the Stability of Perovskite Solar Cells under Harsh Environmental Conditions. *Sol. Energy* **2020**, *202*, 438–445.

(1318) Li, N.; Niu, X.; Chen, Q.; Zhou, H. Towards Commercialization: the Operational Stability of Perovskite Solar Cells. *Chem. Soc. Rev.* **2020**, *49*, 8235–8286.

(1319) Huang, Y.-T.; Kavanagh, S. R.; Scanlon, D. O.; Walsh, A.; Hoye, R. L. Z. Perovskite-Inspired Materials for Photovoltaics – From Design to Devices. *Nanotechnology* **2021**, *32*, 132004.

(1320) Tarascon, J. M.; Armand, M. Issues and Challenges Facing Rechargeable Lithium Batteries. *Nature* **2001**, *414*, 359–367.

(1321) Bruce, P. G.; Freunberger, S. A.; Hardwick, L. J.; Tarascon, J.-M. Erratum: Li–O₂ and Li–S Batteries with High Energy Storage. *Nat. Mater.* **2012**, *11*, 172–172.

(1322) Lewis, N. S.; Nocera, D. G. Powering the planet: Chemical Challenges in Solar Energy Utilization. *Proc. Natl. Acad. Sci. U. S. A.* **2006**, *103*, 15729–15735.

(1323) Nahar, S.; Zain, M. F. M.; Kadhum, A. A. H.; Hasan, H. A.; Hasan, M. R. Advances in Photocatalytic CO₂ Reduction with Water: A Review. *Materials* **2017**, *10*, 629.

(1324) Maeda, K.; Domen, K. Photocatalytic Water Splitting: Recent Progress and Future Challenges. *J. Phys. Chem. Lett.* **2010**, *1*, 2655–2661.

(1325) Stolarczyk, J. K.; Bhattacharyya, S.; Polavarapu, L.; Feldmann, J. Challenges and Prospects in Solar Water Splitting and CO₂ Reduction with Inorganic and Hybrid Nanostructures. *ACS Catal.* **2018**, *8*, 3602–3635.

(1326) Chen, X.; Shen, S.; Guo, L.; Mao, S. S. Semiconductor-Based Photocatalytic Hydrogen Generation. *Chem. Rev.* **2010**, *110*, 6503–6570.

(1327) Kubacka, A.; Fernández-García, M.; Colón, G. Advanced Nanoarchitectures for Solar Photocatalytic Applications. *Chem. Rev.* **2012**, *112*, 1555–1614.

(1328) Huynh, K. A.; Nguyen, D. L. T.; Nguyen, V.-H.; Vo, D.-V. N.; Trinh, Q. T.; Nguyen, T. P.; Kim, S. Y.; Le, Q. V. Halide Perovskite Photocatalysis: Progress and Perspectives. *J. Chem. Technol. Biotechnol.* **2020**, *95*, 2579–2596.

(1329) Park, S.; Chang, W. J.; Lee, C. W.; Park, S.; Ahn, H.-Y.; Nam, K. T. Photocatalytic Hydrogen Generation from Hydriodic Acid using Methylammonium Lead Iodide in Dynamic Equilibrium with Aqueous Solution. *Nat. Energy* **2017**, *2*, 16185.

(1330) Wu, Y.; Wang, P.; Guan, Z.; Liu, J.; Wang, Z.; Zheng, Z.; Jin, S.; Dai, Y.; Whangbo, M.-H.; Huang, B. Enhancing the Photocatalytic Hydrogen Evolution Activity of Mixed-Halide Perovskite CH₃NH₃PbBr_{3-x}I_x Achieved by Bandgap Funneling of Charge Carriers. *ACS Catal.* **2018**, *8*, 10349–10357.

(1331) Zhu, X.; Lin, Y.; Sun, Y.; Beard, M. C.; Yan, Y. Lead-Halide Perovskites for Photocatalytic α -Alkylation of Aldehydes. *J. Am. Chem. Soc.* **2019**, *141*, 733–738.

(1332) Zhu, X.; Lin, Y.; San Martin, J.; Sun, Y.; Zhu, D.; Yan, Y. Lead Halide Perovskites for Photocatalytic Organic Synthesis. *Nat. Commun.* **2019**, *10*, 2843.

(1333) Zhang, Z.; Liang, Y.; Huang, H.; Liu, X.; Li, Q.; Chen, L.; Xu, D. Stable and Highly Efficient Photocatalysis with Lead-Free Double-Perovskite of $\text{Cs}_2\text{AgBiBr}_6$. *Angew. Chem., Int. Ed.* **2019**, *58*, 7263–7267.

(1334) Leng, M.; Chen, Z.; Yang, Y.; Li, Z.; Zeng, K.; Li, K.; Niu, G.; He, Y.; Zhou, Q.; Tang, J. Lead-Free, Blue Emitting Bismuth Halide Perovskite Quantum Dots. *Angew. Chem., Int. Ed.* **2016**, *55*, 15012–15016.

(1335) Lu, C.; Itanze, D. S.; Aragon, A. G.; Ma, X.; Li, H.; Ucer, K. B.; Hewitt, C.; Carroll, D. L.; Williams, R. T.; Qiu, Y.; Geyer, S. M. Synthesis of Lead-Free $\text{Cs}_3\text{Sb}_2\text{Br}_9$ Perovskite Alternative Nanocrystals with Enhanced Photocatalytic CO_2 Reduction Activity. *Nanoscale* **2020**, *12*, 2987–2991.

(1336) Han, C.; Tang, Z.-R.; Liu, J.; Jin, S.; Xu, Y.-J. Efficient Photoredox Conversion of Alcohol to Aldehyde and H_2 by Heterointerface Engineering of Bimetal-Semiconductor Hybrids. *Chem. Sci.* **2019**, *10*, 3514–3522.

(1337) Ou, M.; Tu, W.; Yin, S.; Xing, W.; Wu, S.; Wang, H.; Wan, S.; Zhong, Q.; Xu, R. Amino-Assisted Anchoring of CsPbBr_3 Perovskite Quantum Dots on Porous $\text{g-C}_3\text{N}_4$ for Enhanced Photocatalytic CO_2 Reduction. *Angew. Chem., Int. Ed.* **2018**, *57*, 13570–13574.

(1338) Wu, L.-Y.; Mu, Y.-F.; Guo, X.-X.; Zhang, W.; Zhang, Z.-M.; Zhang, M.; Lu, T.-B. Encapsulating Perovskite Quantum Dots in Iron-Based Metal–Organic Frameworks (MOFs) for Efficient Photocatalytic CO_2 Reduction. *Angew. Chem., Int. Ed.* **2019**, *58*, 9491–9495.

(1339) Dai, Y.; Poidevin, C.; Ochoa-Hernández, C.; Auer, A. A.; Tüysüz, H. A Supported Bismuth Halide Perovskite Photocatalyst for Selective Aliphatic and Aromatic C–H Bond Activation. *Angew. Chem., Int. Ed.* **2020**, *59*, 5788–5796.

(1340) Wang, H.; Wang, X.; Chen, R.; Zhang, H.; Wang, X.; Wang, J.; Zhang, J.; Mu, L.; Wu, K.; Fan, F.; Zong, X.; Li, C. Promoting Photocatalytic H_2 Evolution on Organic–Inorganic Hybrid Perovskite Nanocrystals by Simultaneous Dual-Charge Transportation Modulation. *ACS Energy Lett.* **2019**, *4*, 40–47.

(1341) Pavliuk, M. V.; Abdellah, M.; Sá, J. Hydrogen Evolution with CsPbBr_3 Perovskite Nanocrystals under Visible Light in Solution. *Mater. Today Commun.* **2018**, *16*, 90–96.

(1342) Li, R.; Li, X.; Wu, J.; Lv, X.; Zheng, Y.-Z.; Zhao, Z.; Ding, X.; Tao, X.; Chen, J.-F. Few-Layer Black Phosphorus-on-MAPbI₃ for Superb Visible-Light Photocatalytic Hydrogen Evolution from HI Splitting. *Appl. Catal., B* **2019**, *259*, 118075.

(1343) Wang, Q.; Yu, S.; Qin, W.; Wu, X. Isopropanol-Assisted Synthesis of Highly Stable MAPbBr₃/p-g-C₃N₄ Intergrowth Composite Photocatalysts and Their Interfacial Charge Carrier Dynamics. *Nanoscale Adv.* **2020**, *2*, 274–285.

(1344) Pan, A.; Ma, X.; Huang, S.; Wu, Y.; Jia, M.; Shi, Y.; Liu, Y.; Wangyang, P.; He, L.; Liu, Y. CsPbBr_3 Perovskite Nanocrystal Grown on MXene Nanosheets for Enhanced Photoelectric Detection and Photocatalytic CO_2 Reduction. *J. Phys. Chem. Lett.* **2019**, *10*, 6590–6597.

(1345) Chen, Z.; Hu, Y.; Wang, J.; Shen, Q.; Zhang, Y.; Ding, C.; Bai, Y.; Jiang, G.; Li, Z.; Gaponik, N. Boosting Photocatalytic CO_2 Reduction on CsPbBr_3 Perovskite Nanocrystals by Immobilizing Metal Complexes. *Chem. Mater.* **2020**, *32*, 1517–1525.

(1346) Liu, J.; Song, K.; Shin, Y.; Liu, X.; Chen, J.; Yao, K. X.; Pan, J.; Yang, C.; Yin, J.; Xu, L.-J.; Yang, H.; El-Zohry, A. M.; Xin, B.; Mitra, S.; Hedhili, M. N.; Roqan, I. S.; Mohammed, O. F.; Han, Y.; Bakr, O. M. Light-Induced Self-Assembly of Cubic CsPbBr_3 Perovskite Nanocrystals into Nanowires. *Chem. Mater.* **2019**, *31*, 6642–6649.

(1347) Toso, S.; Baranov, D.; Manna, L. Hidden in Plain Sight: The Overlooked Influence of the Cs⁺ Substructure on Transformations in Cesium Lead Halide Nanocrystals. *ACS Energy Lett.* **2020**, *5*, 3409–3414.

(1348) Cheng, P. F.; Sun, L.; Feng, L.; Yang, S. Q.; Yang, Y.; Zheng, D. Y.; Zhao, Y.; Sang, Y. B.; Zhang, R. L.; Wei, D. H.; Deng, W. Q.; Han, K. L. Colloidal Synthesis and Optical Properties of All-Inorganic Low-Dimensional Cesium Copper Halide Nanocrystals. *Angew. Chem., Int. Ed.* **2019**, *58*, 16087–16091.

(1349) Yin, J.; Bredas, J. L.; Bakr, O. M.; Mohammed, O. F. Boosting Self-Trapped Emissions in Zero-Dimensional Perovskite Heterostructures. *Chem. Mater.* **2020**, *32*, 5036–5043.

(1350) Yang, H.; Zhang, Y.; Pan, J.; Yin, J.; Bakr, O. M.; Mohammed, O. F. Room-Temperature Engineering of All-Inorganic Perovskite Nanocrystals with Different Dimensionalities. *Chem. Mater.* **2017**, *29*, 8978–8982.

(1351) Roh, J. Y. D.; Smith, M. D.; Crane, M. J.; Biner, D.; Milstein, T. J.; Kramer, K. W.; Gamelin, D. R. Yb³⁺ Speciation and Energy-Transfer Dynamics in Quantum-Cutting Yb³⁺-Doped CsPbCl_3 Perovskite Nanocrystals and Single Crystals. *Phys. Rev. Mater.* **2020**, *4*, 105405.

(1352) Xin, Y.; Zhao, H.; Zhang, J. Highly Stable and Luminescent Perovskite–Polymer Composites from a Convenient and Universal Strategy. *ACS Appl. Mater. Interfaces* **2018**, *10*, 4971–4980.

(1353) Steele, J. A.; Pan, W.; Martin, C.; Keshavarz, M.; Debroye, E.; Yuan, H.; Banerjee, S.; Fron, E.; Jonckheere, D.; Kim, C. W.; Baekelant, W.; Niu, G.; Tang, J.; Vanacken, J.; Van der Auweraer, M.; Hofkens, J.; Roeffaers, M. B. J. Photophysical Pathways in Highly Sensitive $\text{Cs}_2\text{AgBiBr}_6$ Double-Perovskite Single-Crystal X-Ray Detectors. *Adv. Mater.* **2018**, *30*, 1804450.

(1354) Ma, J.-P.; Chen, Y.-M.; Zhang, L.-M.; Guo, S.-Q.; Liu, J.-D.; Li, H.; Ye, B.-J.; Li, Z.-Y.; Zhou, Y.; Zhang, B.-B.; Bakr, O. M.; Zhang, J.-Y.; Sun, H.-T. Insights into the local structure of dopants, doping efficiency, and luminescence properties of lanthanide-doped CsPbCl_3 perovskite nanocrystals. *J. Mater. Chem. C* **2019**, *7*, 3037–3048.

(1355) Li, X.; Duan, S.; Liu, H.; Chen, G.; Luo, Y.; Agren, H. Mechanism for the Extremely Efficient Sensitization of Yb³⁺ Luminescence in CsPbCl_3 Nanocrystals. *J. Phys. Chem. Lett.* **2019**, *10*, 487–492.

(1356) Dong, Y.; Zhang, Y.; Li, X.; Feng, Y.; Zhang, H.; Xu, J. Chiral Perovskites: Promising Materials toward Next-Generation Optoelectronics. *Small* **2019**, *15*, 1902237.