



Cite this: DOI: 10.1039/d1ta02565a

Planar defect-driven electrocatalysis of CO₂-to-C₂H₄ conversion†Zhengyuan Li,^a Yanbo Fang,^b Jianfang Zhang,^a Tianyu Zhang,^a Juan D. Jimenez,^{ib} Sanjaya D. Senanayake,^{ib} Vesselin Shanov,^{ab} Shize Yang^{*d} and Jingjie Wu^{ib} ^{*,a}

The selectivity towards a specific C₂₊ product, such as ethylene (C₂H₄), is sensitive to the surface structure of copper (Cu) catalysts in carbon dioxide (CO₂) electro-reduction. The fundamental understanding of such sensitivity can guide the development of advanced electrocatalysts, although it remains challenging at the atomic level. Here we demonstrated that planar defects, such as stacking faults, could drive the electrocatalysis of CO₂-to-C₂H₄ conversion with higher selectivity and productivity than Cu(100) facets in the intermediate potential region (−0.50 ~ −0.65 V vs. RHE). The unique right bipyramidal Cu nanocrystals containing a combination of (100) facets and a set of parallel planar defects delivered 67% faradaic efficiency (FE) for C₂H₄ and a partial current density of 217 mA cm^{−2} at −0.63 V vs. RHE. In contrast, Cu nanocubes with exclusive (100) facets exhibited only 46% FE for C₂H₄ and a partial current density of 87 mA cm^{−2} at an identical potential. Both *ex situ* CO temperature-programmed desorption and *in situ* Raman spectroscopy analysis implied that the stronger *CO adsorption on planar defect sites facilitates CO generation kinetics, which contributes to a higher surface coverage of *CO and in turn an enhanced reaction rate of C–C coupling towards C₂₊ products, especially C₂H₄.

Received 28th March 2021

Accepted 15th June 2021

DOI: 10.1039/d1ta02565a

rsc.li/materials-a

1. Introduction

The CO₂ electro-reduction reaction (CO₂RR) to value-added multi-carbon (C₂₊) products is a promising avenue for artificial carbon recycling using renewable energy sources.^{1,2} In particular, the conversion of CO₂ to ethylene (C₂H₄), a major industrial feedstock with a large market size and relatively high market price,² has received immense attention. Techno-economic analyses (TEAs) reveal that when (1) electricity costs fall below 4 cents kW^{−1} h^{−1}, (2) C₂H₄ partial current density meets 450 mA cm^{−2}, and (3) energy efficiency is at least 60%, the C₂H₄ generated from the CO₂RR becomes competitive with current market prices for that derived from fossil fuel sources.² So far, copper (Cu) and Cu-derived materials have been the most efficient electrocatalysts that can convert CO₂ to C₂₊ products with appreciable reaction rates.³ However, the unsatisfactory selectivity of CO₂ reduction towards a specific high-order product still impedes its large-scale implementation.^{3,4}

It has been demonstrated that the coupling of the key intermediate (*e.g.*, surface adsorbed *CO) is a critical step in CO₂-to-C₂₊ product conversion.^{5–8} Therefore, numerous strategies have been developed to maximize the utilization of *CO. Cascade catalysis involving tandem catalysts,^{9,10} tandem electrodes,^{11,12} and tandem reactors¹³ has been proposed to supply extra CO and thus to raise local CO concentration near the Cu surface for facilitating C–C coupling. Another widely investigated approach is to properly increase the *CO binding energy *via* tuning the surface structures of Cu, such as alloying,¹⁴ surface doping,^{15,16} crystal faceting,^{17,18} subsurface oxygen engineering,¹⁹ and surface reconstruction.²⁰ It is worth noting that the CO generation rate can also be enhanced with the *CO binding energy since the activation energy for CO formation decreases according to the scaling relations and Brønsted–Evans–Polanyi (BEP) relations.²¹ Subsequently, the surface coverage of *CO on Cu can be simultaneously enhanced as *CO binding energy increases.^{5,22,23}

It is well known that the Cu(100) facet with square atomic configurations favors the formation of C₂H₄, which benefits from the stronger *CO binding energy and subsequently lower *CO dimerization barrier compared to that on the Cu(111) facet.⁸ Meanwhile, low-coordinated defect sites, such as vacancies, steps, twin boundaries, and grain boundaries, arisen from *in situ* or *ex situ* growth on the metallic Cu surface were proposed to be responsible for the enhanced catalytic reactivity.^{23–26} Indeed, research on twin boundaries and grain boundaries has pointed out that the high activity and selectivity

^aDepartment of Chemical and Environmental Engineering, University of Cincinnati, Cincinnati, OH 45221, USA. E-mail: jingjie.wu@uc.edu

^bDepartment of Mechanical and Materials Engineering, University of Cincinnati, Cincinnati, OH 45221, USA

^cChemistry Division, Brookhaven National Laboratory, Upton, NY 11973, USA

^dEyring Materials Center, Arizona State University, Tempe, AZ 85287, USA. E-mail: shize.yang@asu.edu

† Electronic supplementary information (ESI) available. See DOI: 10.1039/d1ta02565a

are correlated with the sites binding CO more strongly than low-index Cu facets, and the reactivity is linearly proportional to the density of such active sites.²⁶ But most of these two-dimensional defects are associated with the Cu(111) facets or interfaces between (111) and (100) facets.^{23,27} A comprehensive comparison between (100) facets and planar defects, which is missing, could assist in designing electrocatalysts for further improvement of CO₂-to-C₂₊ conversion.

Herein, we demonstrated that planar defects could drive the electrocatalysis of CO₂-to-C₂H₄ conversion with higher selectivity and productivity than Cu low-index facets. To this end, we prepared a right bipyramidal Cu (Rbp-Cu) electrocatalyst with both exposed Cu(100) facets and a set of parallel planar defects (*e.g.*, stacking faults). Rbp-Cu achieved a Faradaic efficiency (FE) of 67% and 89% for C₂H₄ and C₂₊ products, respectively, at a current density of over 325 mA cm⁻² and a corresponding potential of -0.63 V *vs.* RHE. In contrast, Cu nanocubes (Cube-Cu) with exclusive Cu(100) facets exhibited only 46% FE for C₂H₄ and a partial current density of 87 mA cm⁻² at an identical potential. The planar defect was discovered to show superior activity and selectivity towards C₂H₄ formation to Cu(100) by comparing the performance between Rbp-Cu and Cube-Cu. The reaction mechanism study using CO temperature-programmed desorption and *in situ* Raman spectroscopy implied that the enhancement of reactivity for CO₂-to-C₂H₄ conversion originates from the stronger *CO adsorption energy on planar defects than Cu(100).

2. Experimental

2.1 Chemicals and materials

Copper(II) chloride dehydrate (CuCl₂·2H₂O, 99.0%), D-glucose (C₆H₁₂O₆, 99.5%), hexadecylamine (HDA, 98%), sodium tetrachloropalladate(II) (Na₂PdCl₄, 98%), lead(II) perchlorate hydrate (Pb(ClO₄)₂·xH₂O, 99.995%), perchloric acid (HClO₄, 70%), α-alumina (α-Al₂O₃, 99.9%) and potassium hydroxide (KOH, 99.99%) were obtained from Sigma Aldrich and used as received.

2.2 Synthesis of Cu nanocrystals

The synthetic methods are adapted from previous reports.^{28,29} In a standard synthesis of Rbp-Cu nanocrystals (NCs), 21 mg CuCl₂·2H₂O, 180 mg HDA, 50 mg glucose, 0.2 mg Na₂PdCl₄, and 10 ml water were mixed and magnetically stirred in a 20 ml vial at room temperature overnight. Then Ar was slowly bubbled through the solution for 15 min. After that, the vial was tightly capped and heated at 100 °C for 6 h under magnetic stirring. The as-prepared Rbp-Cu NCs were centrifuged and washed with hexane and ethanol several times. Cube-Cu NCs were prepared following the same procedure, except that the amounts of Na₂PdCl₄ and surfactant (HDA) were adjusted to 0 mg and 90 mg, respectively.

2.3 Characterization

The morphology of the as-prepared Cu NCs was imaged by scanning electron microscopy (SEM, FEI Apreo LV-SEM) and

transmission electron microscopy (TEM, FEI Titan ETEM). The crystalline structure was identified by X-ray diffraction (XRD, Rigaku D/MAX2500VL). The chemical compositions and surface valence states were determined by X-ray photoelectron spectroscopy (XPS, ESCALAB250Xi).

CO temperature-programmed desorption (CO-TPD) was performed under a 10% CO/He atmosphere. The α-alumina support was applied to disperse 10 wt% Cu NCs by a simple impregnation method. 50 mg of Cu samples were first purged with 10% H₂/He at 200 °C for 30 min to remove any impurity on the surface, and then adsorbed CO gas at 50 °C for 60 min. After purging again in pure He at 50 °C to remove physisorbed CO on the sample surface for 60 min, the temperature was raised to 500 °C at a ramp rate of 10 °C min⁻¹. The gas flow rate was fixed at 50 sccm for all steps. The resulting species were traced by on-line mass spectrometry (SRS, RGA 100 Headgas Analyzer). The mass-to-charge (*m/z*) signal of 28 (CO) was monitored with a time interval of 2 s.

2.4 Electrochemical measurements

2.4.1 Lead underpotential deposition. The underpotential deposition of lead (Pb-UPD) was conducted in a three-electrode glass cell at ambient temperature. The Cu NCs loaded on a glassy carbon electrode, Pt mesh, and Ag/AgCl (3 M KCl) were employed as working, counter, and reference electrodes, respectively. A N₂-saturated 0.1 M HClO₄ aqueous solution with 10 mM Pb(ClO₄)₂·xH₂O was used as the electrolyte. Cyclic voltammetry (CV) with a sweep rate of 10 mV s⁻¹ was applied for measurements.

2.4.2 Electrocatalytic measurement of CO₂ reduction. A customized flow cell with 1 M KOH was employed for the CO₂RR under ambient conditions. An FAA-3-PK-75 anion exchange membrane (Fuel Cell Store) was used to separate anodic and cathodic compartments. The cathode was prepared by a spray-coating method. The as-prepared Cu NCs (4 mg) were dispersed in isopropanol (3 ml) and 6 μl Nafion solution (5 wt%). The mixture was sonicated for 30 minutes and air-brushed onto a carbon diffusion layer (GDL, Sigracet 35BC, Fuel Cell Store). The prepared cathode gas diffusion electrode (GDE) was dried at 130 °C under vacuum for 1 h. The catalyst loadings for all samples were kept at around 0.30 mg cm⁻². Ni foam was used as the anode. The electrolyte was fed by using syringe pumps (New Era Pump Systems Inc.) at 1 ml min⁻¹ and 2 ml min⁻¹ to the cathodic and anodic compartments, respectively. CO₂ gas flowed through the cathode at 50 sccm *via* a mass flow controller (Alicat Scientific). A potentiostat (Gamry Interface 1010E) supplied a constant voltage to the flow cell and recorded the corresponding current. The cathode potential was measured relative to the Ag/AgCl (3 M KCl) reference electrode. All potentials were converted to the RHE scale using: $E_{\text{RHE}} = E_{\text{Ag/AgCl}} + 0.209 \text{ V} + 0.0591 \times \text{pH}$. iR compensation was performed by potentiostatic electrochemical impedance spectroscopy (EIS).

For each applied potential, an on-line gas chromatograph (GC, SRI Instruments MultipleGas#5) equipped with both a thermal conductivity detector and a flame ionization detector

was used to monitor the gas products. To calibrate the outlet gas flow rate of CO₂, Ar, as an internal standard, was fed at 10 sccm and mixed with the outlet gas stream from the flow cell before looping to the GC.¹¹ The FEs for gas products were calculated using the following equation (eqn (1)):

$$\text{FE (\%)} = \frac{zFxV}{j_{\text{total}}} \times 100\% \quad (1)$$

where z is the number of electrons transferred for producing a target product; F is the Faraday constant; x is the molar fraction of a target product determined by GC; V is the molar flow rate of gas; j_{total} is the total current density.

Meanwhile, the catholyte was collected after electrolysis followed by quantifying the liquid products *via* ¹H NMR (Bruker AV 400 MHz spectrometer). 500 μl of the catholyte was mixed with a 100 μl internal standard of 5 mM 3-(trimethylsilyl)propionic-2,2,3,3-d₄ acid sodium salt in D₂O. The standard deviations were calculated based on the measurements of three independent electrodes.

The total CO generation and dimerization rates were calculated according to the following two equations (eqn (2) and (3)):

$$\begin{aligned} \text{CO generation rate} = j_{\text{CO}} + \frac{j_{\text{CH}_4}}{4} + \frac{j_{\text{C}_2\text{H}_4}}{3} + \frac{j_{\text{C}_2\text{H}_5\text{OH}}}{3} + \frac{j_{\text{CH}_3\text{COO}^-}}{2} \\ + \frac{j_{\text{C}_3\text{H}_7\text{OH}}}{3} \end{aligned} \quad (2)$$

$$\text{CO dimerization rate} = \frac{j_{\text{C}_2\text{H}_4}}{3} + \frac{j_{\text{C}_2\text{H}_5\text{OH}}}{3} + \frac{j_{\text{CH}_3\text{COO}^-}}{2} + \frac{j_{\text{C}_3\text{H}_7\text{OH}}}{3} \quad (3)$$

2.5 In situ electrochemical Raman spectroscopy measurements

In situ Raman spectroscopy measurements were carried out on a modified flow cell with a quartz window in front of the cathode GDE. Graphite and Ag/AgCl (3 M KCl) were used as counter and reference electrodes, respectively. The cathode and anode were separated by an anion exchange membrane (FAA-3-PK-75). Syringe pumps were used to pump 1 M KOH at 2 ml min⁻¹ to both the cathode and the anode. CO₂ gas was introduced *via* machined flow channels to the back of the GDE at a flow rate of 50 sccm. The Raman spectra were recorded by using a Renishaw inVia Raman microscope with a 785 nm laser. For each *in situ* Raman spectroscopy measurement, the acquisition time was 10 s, and the total accumulation of scans was 30. Cathode potentials were applied in the potentiostatic mode and converted to the RHE scale accordingly. The samples were initially activated under CO₂RR conditions for 15 min before starting *in situ* Raman spectroscopy measurements.

3. Results and discussion

The Rbp-Cu NCs, which contain Cu(100) facets and abundant planar defects exposed simultaneously, were synthesized by a one-step reduction process using HDA as the capping agent.²⁸

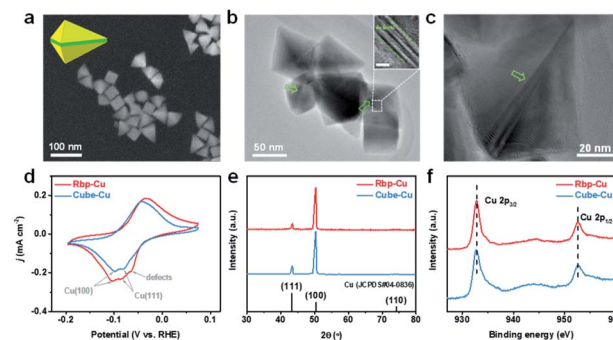


Fig. 1 (a) SEM image of Rbp-Cu. Inset shows the schematic model of an individual Rbp-Cu. Yellow and green represent (100) facets and planar defects, respectively. (b) TEM image of Rbp-Cu. The arrows denote the planar defects. Inset shows a zoomed-in TEM image taken from the box region. Inset scale bar: 5 nm. (c) TEM image of a Rbp-Cu NC highlighting triangular (100) facets bisected by planar defects. (d) Pb-UPD profiles at a scan rate of 10 mV s⁻¹, (e) XRD, and (f) Cu 2p XPS spectrum of Rbp-Cu and Cube-Cu.

In comparison, the Cube-Cu NCs with exclusive Cu(100) facet surfaces were prepared following the same procedure except for regulating the amount of reactants.²⁹ As shown in SEM images (Fig. 1a), the Rbp-Cu NCs possess a particle size of 60–80 nm with several typical projected profiles, such as triangle, rhombus, and tetragon. Additional high-magnification SEM images and schematic models of individual Rbp-Cu in different orientations are shown in the ESI (Fig. S1†). TEM images unraveled the existence of parallel planar defects (*e.g.*, stacking faults) on the Rbp-Cu surface (Fig. 1b, c and S2, ESI†). Alternating light/dark contrasts in the inset of Fig. 1b are typically a set of stacking faults.³⁰ Analogous to the right bipyramid structures of Ag and Pd,^{31,32} each Rbp-Cu NC is bounded by six triangular (100) side facets (yellow in the Rbp model in the inset of Fig. 1a) and is mirror-symmetrically divided by a set of planar defects (green in the Rbp model in the inset of Fig. 1a). Benefiting from the regular morphologies of Rbp-Cu, the proportion of planar defects is calculated to be 20.1% based on the geometric dimensions for a typical Rbp-Cu NC (Fig. S2c†). As expected, the as-prepared Cube-Cu with a particle size of 80–120 nm, as a control sample, exhibits a regular cubic shape with (100) facets (Fig. S3†).

We used Pb underpotential deposition (UPD), a surface-sensitive electrochemical technique, to further probe the surface structures of Cu NCs. Different Cu facets exhibit distinguished Pb-UPD peaks in the CV curves.^{17,33} As displayed in Fig. 1d, the peaks located at *ca.* −0.10 V and −0.08 V can be assigned to Cu(100) and Cu(111), respectively.¹⁷ The peaks of Pb electrodeposition on Cu(100) are more prominent for both Rbp-Cu and Cube-Cu samples than those on Cu(111). An additional peak centered at a less cathodic potential (*ca.* −0.06 V) is only observed for Rbp-Cu, which is ascribed to the Pb-UPD on the low-coordinated sites from surface defects.^{33,34} Such a kind of phenomenon that the Pb over-layer on the face-centered cubic metal preferentially nucleates at the edges or steps and then expands to the terraces has been demonstrated by *in situ*

scanning probe microscopy studies.³⁵ OH^- electro-adsorption was also performed to verify the predominant (100) facets for both Cu NCs (Fig. S4†). An additional shoulder peak at *ca.* 0.34 V was observed for Rbp-Cu, which is associated with surface defects.³⁶ The percent of high-index surface defects on Rbp-Cu is estimated to be 17.3% according to the integral peak areas,³⁷ which is close to the value obtained from TEM aforementioned. In agreement with TEM, Pb-UPD and OH^- electro-adsorption results confirm the presence of defect sites on Rbp-Cu, although the exact facet index is hard to identify. XRD patterns show that both types of Cu NCs exhibit a much more pronounced (100) peak and a weaker (111) peak (Fig. 1e), which is consistent with electrochemical characterization results and confirms the uniform shape of the NCs. Moreover, other than Cu peaks, no other peaks associated with copper oxide or other impurities were observed. XPS analysis reveals that Rbp-Cu and Cube-Cu both present two main peaks at 932.8 eV and 952.6 eV in the Cu 2p spectrum (Fig. 1f), corresponding to Cu^0 or Cu^+ species.³⁸ The Auger Cu LMM spectrum (Fig. S5†) shows that both Rbp-Cu and Cube-Cu mainly consist of Cu^0 (918.6 eV) at the surface, with a minimal amount of Cu^+ (916.6 eV). The formation of Cu^+ is caused by the rapid oxidation of Cu^0 in air and would be quickly *in situ* reduced to metallic Cu under CO_2 electrolysis.^{22,39} Due to the introduction of a trace amount of Pd (<0.55 at%) as the seed during the synthesis of Rbp-Cu, Pd 3d XPS was carried out. There is no Pd element on the Rbp-Cu surface (Fig. S6†), suggesting the absence of Pd dopants or Pd-Cu bimetallic structures.

The CO_2RR performance on Rbp-Cu and Cube-Cu based GDEs was measured in a customized flow cell using 1 M KOH as the catholyte (Fig. S7 and S8†). Rbp-Cu exhibited a higher selectivity towards C_2H_4 than Cube-Cu. The maximum FE of C_2H_4 for Rbp-Cu reached 67% at -0.63 V (vs. RHE, thereafter), at which the partial current density ($j_{\text{C}_2\text{H}_4}$) reached 217 mA cm^{-2} (Fig. 2a and b). The overall performance of Rbp-Cu for CO_2 -to- C_2H_4 conversion is superior to that of most copper-based catalysts tested under identical conditions (Table S1†). Combined with C_{2+} liquid products analyzed by ^1H NMR, including ethanol ($\text{C}_2\text{H}_5\text{OH}$), acetate (CH_3COO^-), and *n*-propene ($\text{C}_3\text{H}_7\text{OH}$), the FE and partial current density of C_{2+} products ($j_{\text{C}_{2+}}$) on Rbp-Cu reached 89% and 289 mA cm^{-2} , respectively, at -0.63 V (Fig. 2c and d). In contrast, Cube-Cu showed only 46% FE for C_2H_4 and 68% FE for C_{2+} products at the same overpotential. Moreover, the FE ratio of C_2H_4 over $\text{C}_2\text{H}_5\text{OH}$ was enhanced from 3.10 for Cube-Cu to 3.77 for Rbp-Cu at -0.63 V (Fig. S9†). Compared to Rbp-Cu, Cube-Cu manifested lower $j_{\text{C}_2\text{H}_4}$ and $j_{\text{C}_{2+}}$ over the applied potential range (Fig. 2b and d). Interestingly, we found that Rbp-Cu showed a relatively much lower FE for CO than Cube-Cu (Fig. S10†), indicating the more efficient conversion of the $^*\text{CO}$ intermediate to hydrocarbons and oxygenates on Rbp-Cu.¹⁰ The improvement of activity and selectivity towards C_2H_4 and C_{2+} products suggests that the planar defect sites on Rbp-Cu may be responsible for the enhanced C-C coupling rate.

To exclude the possible effect of surface roughness, the electrochemical surface area (ECSA) was determined by using the double-layer capacitance (C_{dl}) method (Fig. S11†). The ECSA

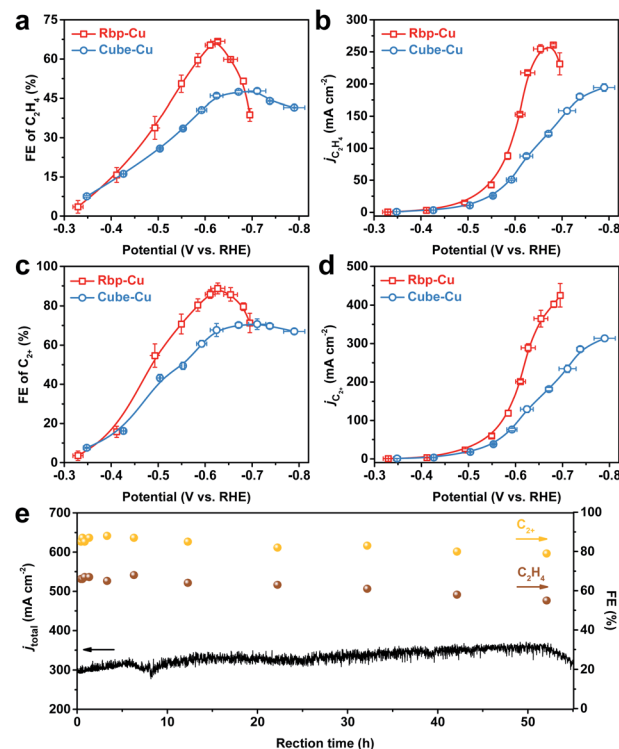


Fig. 2 Comparison of the CO_2RR performance of Rbp-Cu and Cube-Cu. (a–d) The potential-dependent (a) FE for C_2H_4 , (b) $j_{\text{C}_2\text{H}_4}$, (c) FE for C_{2+} products, and (d) $j_{\text{C}_{2+}}$. The error bars represent the standard deviation based on the measurements of three independent electrodes. (e) The stability of Rbp-Cu operated at -0.63 V vs. RHE.

normalized current density of each product followed the same trend as the geometric current density for both Rbp-Cu and Cube-Cu (Fig. S12†). At an optimal potential of -0.63 V for C_2H_4 and C_{2+} product formation, the normalized $j_{\text{C}_2\text{H}_4}$ and $j_{\text{C}_{2+}}$ for Rbp-Cu were 1.9-fold and 1.7-fold higher than those for Cube-Cu, respectively, indicating the excellent intrinsic activity of Rbp-Cu towards C_2H_4 and C_{2+} products. Considering a lower surface-to-volume ratio of Cube-Cu related to Rbp-Cu,²⁸ the loading of Cube-Cu was increased from 0.30 to 0.42 mg cm^{-2} , which increased the C_{dl} (proportional to the ECSA) to 0.57 mF cm^{-2} accordingly, similar to that of Rbp-Cu (0.56 mF cm^{-2}) with a loading of 0.30 mg cm^{-2} (Fig. S13†). Although the current density increased with the catalyst loading, a similar product distribution was obtained for Cube-Cu with two different loadings. Especially, the FEs for C_2H_4 were almost identical in the investigated overpotential range (Fig. S13e†). Therefore, we infer that a higher ECSA is not the main factor for promoting selectivity towards C_2H_4 .

Notably, Rbp-Cu exhibited activity towards C_2H_4 and C_{2+} products similar to Cube-Cu at potentials between -0.35 and -0.50 V (Fig. 2 and S12†), likely owing to the Cu(100) facet on both Cu NCs which facilitates the $^*\text{COCO}$ dimerization in such a low overpotential region.^{7,39} In the potential region of $-0.50 \sim -0.65$ V, the planar defect sites on the Rbp-Cu surface play a more critical role in CO_2 -to- C_{2+} product conversion. The possible dimerization pathways in this overpotential range may

involve coupling between $^*\text{CO}$ and reduced $^*\text{CO}$ species (*i.e.*, $^*\text{CHO}$ and/or $^*\text{COH}$),^{8,40} the reaction barrier of which could be decreased on low-coordinated defects.^{37,41,42} However, the selectivity towards C_2H_4 for Rbp-Cu decreased dramatically at higher cathodic potentials ($-0.65 \sim -0.70$ V). Simultaneously, the activity and selectivity towards hydrogen (H_2) and methane (CH_4) rose accordingly (Fig. S10 and S12†). The upsurge of reactivity towards H_2 arises from the stronger competitive hydrogen evolution reaction (HER) occurring on low-coordinated sites in the high cathodic potential region.^{30,43} To verify this, the HER was performed under an Ar atmosphere in a flow cell. Linear sweep voltammetry (LSV) showed higher electrocatalytic activity of Rbp-Cu for the HER than Cube-Cu as the potential was swept beyond -0.50 V (Fig. S14†), demonstrating that planar defects are more active for the HER as well as the CO_2RR in the high cathodic potential region. At higher overpotentials, increased adsorption of hydrogen would suppress CO_2 -to- C_{2+} product conversion.⁴⁴

To demonstrate a stable CO_2 -to- C_{2+} product conversion, a durability test for Rbp-Cu was conducted at -0.63 V, where optimal selectivity towards C_2H_4 and C_{2+} products was achieved. By using polytetrafluoroethylene-treated GDL to improve the hydrophobicity, a relatively stable FE of $(61 \pm 5)\%$ for C_2H_4 was recorded while FE for C_{2+} products was maintained at $(82 \pm 4)\%$ with a total current density of $(330 \pm 30) \text{ mA cm}^{-2}$ during a 50 hour continuous test (Fig. 2e). As examined by TEM, the post-electrolysis Rbp-Cu retained the planar defects (Fig. S15†), although the corners or edges of the well-defined morphology were degraded to some extent.^{45,46} Surface adsorbed $^*\text{CO}$, the key intermediate for CO_2 reduction to hydrocarbons and oxygenates, may stabilize Cu defects in line with prior density functional theory (DFT) calculations.²²

Given that the same Cu(100) facets were exposed for both Rbp-Cu and Cube-Cu samples, we envisioned that the superior CO_2 -to- C_2H_4 conversion is attributed to the introduction of the planar defects on the Rbp-Cu surface. These planar defects with a low coordination number enable stronger $^*\text{CO}$ adsorption that assists in building a sufficiently high surface coverage of $^*\text{CO}$ to direct the C-C coupling.^{6,23} To prove this hypothesis, an *ex situ* CO-TPD experiment and *in situ* electrochemical Raman spectroscopy measurements were conducted.

The monitored CO-TPD traces, which can give the amount and strength of $^*\text{CO}$ adsorption, are shown in Fig. 3a and S16.† For both types of Cu NCs, the onset CO desorption began at approximately 60°C . The observation of a later CO desorption peak at 90°C for Rbp-Cu indicates a stronger adsorption affinity for CO and CO-related intermediates, resulting from the presence of planar defects.^{36,47} Additionally, the larger CO desorption peak area for Rbp-Cu implies a larger surface coverage of $^*\text{CO}$ on Rbp-Cu than Cube-Cu.⁴⁸ These CO-TPD results preliminarily support that both the adsorption energy and surface coverage of $^*\text{CO}$ are boosted on Rbp-Cu, benefiting from planar defect sites.

To evaluate the $^*\text{CO}$ adsorption behaviors under CO_2 electrocatalysis conditions, *in situ* Raman spectroscopy measurements were further carried out in a modified flow cell with a quartz window in front of the cathode GDE (Fig. 3b). The

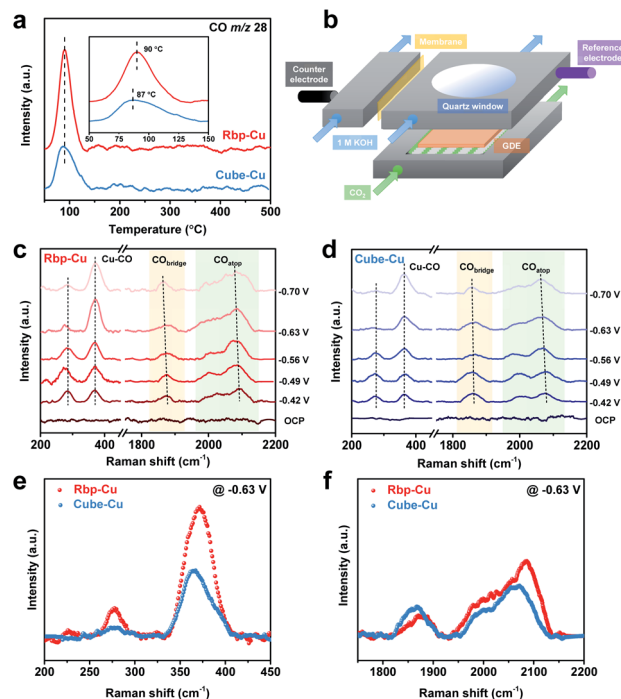


Fig. 3 (a) CO-TPD profiles of Rbp-Cu and Cube-Cu. The desorption compound is monitored with an m/z ratio of 28 for CO. Inset shows the zoomed-in region from 50 to 150°C . (b) Schematic of the *in situ* Raman spectroscopy flow cell. (c, d) *In situ* Raman spectroscopy of (c) Rbp-Cu and (d) Cube-Cu during the CO_2RR at different applied potentials. All the given potentials are referred to the RHE. (e, f) Comparison of *in situ* Raman spectra for Rbp-Cu and Cube-Cu in the (e) low-frequency range and (f) high-frequency range at -0.63 V vs. RHE.

Raman spectra were recorded in a range of applied potentials from the open circuit potential (OCP) to -0.70 V for both types of Cu NCs (Fig. 3c and d). For Rbp-Cu, the low-frequency bands of $^*\text{CO}$ at *ca.* 282 and 371 cm^{-1} are characteristic of Cu-CO frustrated rotation and Cu-CO stretch, respectively (Fig. 3e).⁴⁹ The high-frequency bands are associated with $\text{C}\equiv\text{O}$ stretching vibrations with different adsorption configurations, including bridge-bound CO ($\text{CO}_{\text{bridge}}$, $1850\text{--}1880 \text{ cm}^{-1}$) and atop-bound CO (CO_{atop} , $2000\text{--}2090 \text{ cm}^{-1}$).^{49,50} Notably, the asymmetric broad band for CO_{atop} is likely due to the $^*\text{CO}$ adsorption on various Cu surface sites, which, in turn, may affect the activity and selectivity of the CO_2RR .^{49,51} The difference in $^*\text{CO}$ adsorption behaviors between Rbp-Cu and Cube-Cu was assessed by comparing the *in situ* Raman spectra collected at the same applied potential of -0.63 V. First, a blue shift of the CO_{atop} sharp band suggests the stronger binding of $^*\text{CO}$ at low-coordinated defect sites for Rbp-Cu (2084 cm^{-1}) relative to Cube-Cu (2067 cm^{-1}) (Fig. 3f).⁴⁹ Meanwhile, the band for the Cu-CO stretch also exhibited a blue shift on Rbp-Cu (371 cm^{-1}) compared to that on Cube-Cu (365 cm^{-1}) (Fig. 3e), confirming a stronger binding of $^*\text{CO}$ to the Rbp-Cu surface.⁵² Second, the integrated areas of bands (*e.g.*, Cu-CO and CO_{atop} bands), which are proportional to the $^*\text{CO}$ surface coverage,⁴⁹ increase for Rbp-Cu compared with Cube-Cu (Fig. 3e and f). Taken together, *ex*

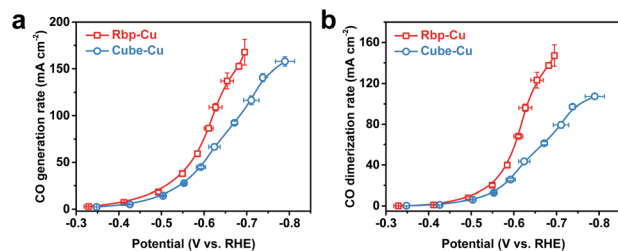


Fig. 4 Comparison of the (a) CO generation rate and (b) CO dimerization rate between Rbp-Cu and Cube-Cu at different applied potentials.

situ CO-TPD and the *in situ* Raman spectroscopy results unravel that Rbp-Cu promotes the adsorption and surface coverage of $^*\text{CO}$, which could enhance the subsequent C–C coupling kinetics and thus the production of C_{2+} products.

To further explore the impact of the enhancement of $^*\text{CO}$ adsorption energy on the C–C coupling kinetics, we analyzed and compared the CO generation and dimerization rates (Fig. 4 and S17†).¹² The CO generation rate was referred to as the summary of the normalized production rates of CO, CH_4 , and C_{2+} products (eqn (2) in the Experimental section). According to the scaling relations of adsorption energy between intermediates and BEP relations between the intermediate adsorption energy and activation barrier,²¹ the enhancement of $^*\text{CO}$ binding indicates stronger $^*\text{COOH}$ binding and a lower activation barrier in the elementary step of CO_2 -to- $^*\text{COOH}$ conversion, which leads to an accelerated CO generation rate. Fig. 4a shows that Rbp-Cu indeed provided more CO than Cube-Cu, manifesting that planar defects facilitate the CO generation rate compared to terraces such as (100) facets in our case. Meanwhile, the CO dimerization rate was derived based on the normalized production rates of C_{2+} products (eqn (3) in the Experimental section). Again, Rbp-Cu exhibited a much faster CO dimerization rate than Cube-Cu due partly to the increased surface coverage of $^*\text{CO}$ (Fig. 4b). For example, the CO dimerization rate of Rbp-Cu reached >2.2-times as high as that of Cube-Cu at around -0.65 V. It is also reasonable to propose that C–C coupling intermediates, such as $^*\text{COCO}$, $^*\text{COCHO}$, or $^*\text{COCO}$, can be efficiently stabilized on defect sites, which further facilitates the dimerization reaction.^{40,41} In short, compared to (100) facets, the stronger $^*\text{CO}$ adsorption on planar defect sites facilitates CO generation kinetics in the intermediate overpotential region, which contributes to a higher surface coverage of $^*\text{CO}$ and in turn an enhanced reaction rate of C–C coupling towards C_{2+} products, especially C_2H_4 .

4. Conclusions

In summary, compared to a regular Cube-Cu NC with exclusive (100) facets, Rbp-Cu, containing a combination of planar defects (*e.g.*, stacking faults) and (100) facets, exhibits a higher selectivity to C_2H_4 (FE = 67%) and C_{2+} products (FE = 89%) with a corresponding $j_{\text{C}_2\text{H}_4}$ of 217 mA cm^{-2} at -0.63 V. Using CO-

TPD and *in situ* Raman spectroscopy, the introduction of planar defects on the Rbp-Cu surface is found to contribute to the increase of $^*\text{CO}$ adsorption energy and $^*\text{CO}$ surface coverage. Based on CO generation and dimerization rates analysis, a stronger $^*\text{CO}$ binding facilitates the $^*\text{CO}$ surface coverage and promotes the C–C coupling kinetics. Additionally, a durability test illustrates that defects are stabilized by $^*\text{CO}$ under CO_2RR conditions. Further DFT investigations are expected to explore the relationship between specific active sites and favorable reaction pathways to either C_2H_4 or $\text{C}_2\text{H}_5\text{OH}$ at the atomic level. Nevertheless, this work provides an in-depth insight into the reactivity comparison between planar defects and Cu(100) facets, which guides the design of advanced catalysts for efficient CO_2 -to- C_2H_4 conversion.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work was financially supported by NSF CBET-2033343. S. Y. acknowledges the use of facilities within the Eyring Materials Center at Arizona State University supported in part by NNCI-ECCS-1542160. J. J. and S. S. acknowledge that the research carried out at the Brookhaven National Laboratory (BNL) was supported by the Division of Chemical Science, Geoscience, and Bioscience, Office of Basic Energy Science of the US Department of Energy (DOE), under contract no. DE-SC0012704.

Notes and references

- Y. Y. Birdja, E. Pérez-Gallent, M. C. Figueiredo, A. J. Göttle, F. Calle-Vallejo and M. T. M. Koper, *Nat. Energy*, 2019, **4**, 732–745.
- P. D. Luna, C. Hahn, D. Higgins, S. A. Jaffer, T. F. Jaramillo and E. H. Sargent, *Science*, 2019, **364**, eaav3506.
- S. Nitopi, E. Bertheussen, S. B. Scott, X. Liu, A. K. Engstfeld, S. Horch, B. Seger, I. E. L. Stephens, K. Chan, C. Hahn, J. K. Nørskov, T. F. Jaramillo and I. Chorkendorff, *Chem. Rev.*, 2019, **119**, 7610–7672.
- R. I. Masel, Z. Liu, H. Yang, J. J. Kaczur, D. Carrillo, S. Ren, D. Salvatore and C. P. Berlinguette, *Nat. Nanotechnol.*, 2021, **16**, 118–128.
- Y. Huang, A. D. Handoko, P. Hirunsit and B. S. Yeo, *ACS Catal.*, 2017, **7**, 1749–1756.
- R. B. Sandberg, J. H. Montoya, K. Chan and J. K. Nørskov, *Surf. Sci.*, 2016, **654**, 56–62.
- J. H. Montoya, C. Shi, K. Chan and J. K. Nørskov, *J. Phys. Chem. Lett.*, 2015, **6**, 2032–2037.
- F. Calle-Vallejo and M. T. M. Koper, *Angew. Chem., Int. Ed.*, 2013, **52**, 7282–7285.
- D. Ren, B. S.-H. Ang and B. S. Yeo, *ACS Catal.*, 2016, **6**, 8239–8247.
- Z. Li, R. M. Yadav, L. Sun, T. Zhang, J. Zhang, P. M. Ajayan and J. Wu, *Appl. Catal., A*, 2020, **606**, 117829.

- 11 X. She, T. Zhang, Z. Li, H. Li, H. Xu and J. Wu, *Cell Rep. Phys. Sci.*, 2020, **1**, 100051.
- 12 T. Zhang, Z. Li, J. Zhang and J. Wu, *J. Catal.*, 2020, **387**, 163–169.
- 13 A. Ozden, Y. Wang, F. Li, M. Luo, J. Sisler, A. Thevenon, A. Rosas-Hernández, T. Burdyny, Y. Lum, H. Yadegari, T. Agapie, J. C. Peters, E. H. Sargent and D. Sinton, *Joule*, 2021, **5**, 706–719.
- 14 M. Zhong, K. Tran, Y. Min, C. Wang, Z. Wang, C.-T. Dinh, P. De Luna, Z. Yu, A. S. Rasouli, P. Brodersen, S. Sun, O. Voznyy, C.-S. Tan, M. Askerka, F. Che, M. Liu, A. Seifitokaldani, Y. Pang, S.-C. Lo, A. Ip, Z. Ulissi and E. H. Sargent, *Nature*, 2020, **581**, 178–183.
- 15 Y. Zhou, F. Che, M. Liu, C. Zou, Z. Liang, P. De Luna, H. Yuan, J. Li, Z. Wang, H. Xie, H. Li, P. Chen, E. Bladt, R. Quintero-Bermudez, T.-K. Sham, S. Bals, J. Hofkens, D. Sinton, G. Chen and E. H. Sargent, *Nat. Chem.*, 2018, **10**, 974–980.
- 16 W. Ma, S. Xie, T. Liu, Q. Fan, J. Ye, F. Sun, Z. Jiang, Q. Zhang, J. Cheng and Y. Wang, *Nat. Catal.*, 2020, **3**, 478–487.
- 17 Y. Wang, Z. Wang, C.-T. Dinh, J. Li, A. Ozden, M. Golam Kibria, A. Seifitokaldani, C.-S. Tan, C. M. Gabardo, M. Luo, H. Zhou, F. Li, Y. Lum, C. McCallum, Y. Xu, M. Liu, A. Proppe, A. Johnston, P. Todorovic, T.-T. Zhuang, D. Sinton, S. O. Kelley and E. H. Sargent, *Nat. Catal.*, 2020, **3**, 98–106.
- 18 G. L. De Gregorio, T. Burdyny, A. Loiudice, P. Iyengar, W. A. Smith and R. Buonsanti, *ACS Catal.*, 2020, **10**, 4854–4862.
- 19 S.-C. Lin, C.-C. Chang, S.-Y. Chiu, H.-T. Pai, T.-Y. Liao, C.-S. Hsu, W.-H. Chiang, M.-K. Tsai and H. M. Chen, *Nat. Commun.*, 2020, **11**, 3525.
- 20 H. Jung, S. Y. Lee, C. W. Lee, M. K. Cho, D. H. Won, C. Kim, H.-S. Oh, B. K. Min and Y. J. Hwang, *J. Am. Chem. Soc.*, 2019, **141**, 4624–4633.
- 21 A. H. Motagamwala and J. A. Dumesic, *Chem. Rev.*, 2021, **121**, 1049–1076.
- 22 Z. Gu, H. Shen, Z. Chen, Y. Yang, C. Yang, Y. Ji, Y. Wang, C. Zhu, J. Liu, J. Li, T.-K. Sham, X. Xu and G. Zheng, *Joule*, 2021, **5**, 429–440.
- 23 C. Choi, T. Cheng, M. F. Espinosa, H. Fei, X. Duan, W. A. Goddard and Y. Huang, *Adv. Mater.*, 2019, **31**, 1805405.
- 24 B. Zhang, J. Zhang, M. Hua, Q. Wan, Z. Su, X. Tan, L. Liu, F. Zhang, G. Chen, D. Tan, X. Cheng, B. Han, L. Zheng and G. Mo, *J. Am. Chem. Soc.*, 2020, **142**, 13606–13613.
- 25 C. W. Li, J. Ciston and M. W. Kanan, *Nature*, 2014, **508**, 504–507.
- 26 X. Feng, K. Jiang, S. Fan and M. W. Kanan, *ACS Cent. Sci.*, 2016, **2**, 169–174.
- 27 Y. Pang, J. Li, Z. Wang, C.-S. Tan, P.-L. Hsieh, T.-T. Zhuang, Z.-Q. Liang, C. Zou, X. Wang, P. De Luna, J. P. Edwards, Y. Xu, F. Li, C.-T. Dinh, M. Zhong, Y. Lou, D. Wu, L.-J. Chen, E. H. Sargent and D. Sinton, *Nat. Catal.*, 2019, **2**, 251–258.
- 28 Z. Lyu, M. Xie, K. D. Gilroy, Z. D. Hood, M. Zhao, S. Zhou, J. Liu and Y. Xia, *Chem. Mater.*, 2018, **30**, 6469–6477.
- 29 M. Jin, G. He, H. Zhang, J. Zeng, Z. Xie and Y. Xia, *Angew. Chem., Int. Ed.*, 2011, **50**, 10560–10564.
- 30 Z. Li, J.-Y. Fu, Y. Feng, C.-K. Dong, H. Liu and X.-W. Du, *Nat. Catal.*, 2019, **2**, 1107–1114.
- 31 J. Zhang, S. Li, J. Wu, G. C. Schatz and C. A. Mirkin, *Angew. Chem., Int. Ed.*, 2009, **48**, 7787–7791.
- 32 X. Xia, S.-I. Choi, J. A. Herron, N. Lu, J. Scaranto, H.-C. Peng, J. Wang, M. Mavrikakis, M. J. Kim and Y. Xia, *J. Am. Chem. Soc.*, 2013, **135**, 15706–15709.
- 33 C. Kim, T. Möller, J. Schmidt, A. Thomas and P. Strasser, *ACS Catal.*, 2019, **9**, 1482–1488.
- 34 S. Mezzavilla, S. Horch, I. E. L. Stephens, B. Seger and I. Chorkendorff, *Angew. Chem., Int. Ed.*, 2019, **58**, 3774–3778.
- 35 E. Herrero, L. J. Buller and H. D. Abruña, *Chem. Rev.*, 2001, **101**, 1897–1930.
- 36 D. Raciti, L. Cao, K. J. T. Livi, P. F. Rottmann, X. Tang, C. Li, Z. Hicks, K. H. Bowen, K. J. Hemker, T. Mueller and C. Wang, *ACS Catal.*, 2017, **7**, 4467–4472.
- 37 C. Choi, S. Kwon, T. Cheng, M. Xu, P. Tieu, C. Lee, J. Cai, H. M. Lee, X. Pan, X. Duan, W. A. Goddard and Y. Huang, *Nat. Catal.*, 2020, **3**, 804–812.
- 38 A. F. Carley, L. A. Dollard, P. R. Norman, C. Pottage and M. W. Roberts, *J. Electron Spectrosc. Relat. Phenom.*, 1999, **98–99**, 223–233.
- 39 T.-T. Zhuang, Y. Pang, Z.-Q. Liang, Z. Wang, Y. Li, C.-S. Tan, J. Li, C. T. Dinh, P. De Luna, P.-L. Hsieh, T. Burdyny, H.-H. Li, M. Liu, Y. Wang, F. Li, A. Proppe, A. Johnston, D.-H. Nam, Z.-Y. Wu, Y.-R. Zheng, A. H. Ip, H. Tan, L.-J. Chen, S.-H. Yu, S. O. Kelley, D. Sinton and E. H. Sargent, *Nat. Catal.*, 2018, **1**, 946–951.
- 40 J. D. Goodpaster, A. T. Bell and M. Head-Gordon, *J. Phys. Chem. Lett.*, 2016, **7**, 1471–1477.
- 41 Z. Chen, T. Wang, B. Liu, D. Cheng, C. Hu, G. Zhang, W. Zhu, H. Wang, Z.-J. Zhao and J. Gong, *J. Am. Chem. Soc.*, 2020, **142**, 6878–6883.
- 42 D. Cheng, Z.-J. Zhao, G. Zhang, P. Yang, L. Li, H. Gao, S. Liu, X. Chang, S. Chen, T. Wang, G. A. Ozin, Z. Liu and J. Gong, *Nat. Commun.*, 2021, **12**, 395.
- 43 R. Reske, H. Mistry, F. Beharfarid, B. Roldan Cuenya and P. Strasser, *J. Am. Chem. Soc.*, 2014, **136**, 6978–6986.
- 44 X. Liu, P. Schlexer, J. Xiao, Y. Ji, L. Wang, R. B. Sandberg, M. Tang, K. S. Brown, H. Peng, S. Ringe, C. Hahn, T. F. Jaramillo, J. K. Nørskov and K. Chan, *Nat. Commun.*, 2019, **10**, 32.
- 45 J. Huang, N. Hörmann, E. Oveisi, A. Loiudice, G. L. De Gregorio, O. Andreussi, N. Marzari and R. Buonsanti, *Nat. Commun.*, 2018, **9**, 3117.
- 46 M. de Jesus Gálvez-Vázquez, P. Moreno-García, H. Xu, Y. Hou, H. Hu, I. Z. Montiel, A. V. Rudnev, S. Alinejad, V. Grozovski, B. J. Wiley, M. Arenz and P. Broekmann, *ACS Catal.*, 2020, **10**, 13096–13108.
- 47 S. Vollmer, G. Witte and C. Wöll, *Catal. Lett.*, 2001, **77**, 97–101.
- 48 J. Strunk, R. N. d'Alnoncourt, M. Bergmann, S. Litvinov, X. Xia, O. Hinrichsen and M. Muhler, *Phys. Chem. Chem. Phys.*, 2006, **8**, 1556–1565.

- 49 C. M. Gunathunge, X. Li, J. Li, R. P. Hicks, V. J. Ovalle and M. M. Waagele, *J. Phys. Chem. C*, 2017, **121**, 12337–12344.
- 50 X. Chang, Y. Zhao and B. Xu, *ACS Catal.*, 2020, **10**, 13737–13747.
- 51 C. M. Gunathunge, V. J. Ovalle, Y. Li, M. J. Janik and M. M. Waagele, *ACS Catal.*, 2018, **8**, 7507–7516.
- 52 X. Wang, Z. Wang, F. P. García de Arquer, C.-T. Dinh, A. Ozden, Y. C. Li, D.-H. Nam, J. Li, Y.-S. Liu, J. Wicks, Z. Chen, M. Chi, B. Chen, Y. Wang, J. Tam, J. Y. Howe, A. Proppe, P. Todorović, F. Li, T.-T. Zhuang, C. M. Gabardo, A. R. Kirmani, C. McCallum, S.-F. Hung, Y. Lum, M. Luo, Y. Min, A. Xu, C. P. O'Brien, B. Stephen, B. Sun, A. H. Ip, L. J. Richter, S. O. Kelley, D. Sinton and E. H. Sargent, *Nat. Energy*, 2020, **5**, 478–486.