

pubs.acs.org/NanoLett Letter

# Moiré Skyrmions and Chiral Magnetic Phases in Twisted $CrX_3$ (X = I, Br, and Cl) Bilayers

Muhammad Akram,<sup>†</sup> Harrison LaBollita,<sup>†</sup> Dibyendu Dey, Jesse Kapeghian, Onur Erten,\* and Antia S. Botana\*



Cite This: Nano Lett. 2021, 21, 6633-6639




**ACCESS** 

Metrics & More

Article Recommendations

Supporting Information

**ABSTRACT:** We present a comprehensive theory of the magnetic phases in twisted bilayer chromium trihalides through a combination of first-principles calculations and atomistic simulations. We show that the stacking-dependent interlayer exchange leads to an effective moiré field that is mostly ferromagnetic with antiferromagnetic patches. A wide range of noncollinear magnetic phases can be stabilized as a function of the twist angle and Dzyaloshinskii—Moriya interaction as a result of the competing interlayer antiferromagnetic coupling and the energy cost for forming domain walls. In particular, we demonstrate that for small twist angles various skyrmion crystal phases can be stabilized in both CrI<sub>3</sub> and CrBr<sub>3</sub>. Our results provide an interpretation for the recent observation of noncollinear magnetic phases in twisted bilayer CrI<sub>3</sub> and demonstrate the possibility of engineering further nontrivial magnetic ground states in twisted bilayer chromium trihalides.

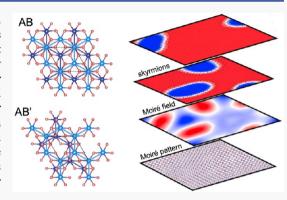

**KEYWORDS:** 2D vdW magnets,  $CrX_3$  (X = I, Br, and Cl), moiré patterns, skyrmions

oiré superlattices arising from twisted bilayers of van der Waals (vdW) crystals represent an ideal platform for studying a plethora of novel phenomena: from the discovery of unconventional superconductivity in twisted bilayer graphene to the recent prediction of noncollinear magnetic states in two-dimensional (2D) magnetic materials.2-5 Among the currently known 2D vdW magnets, chromium trihalides (CrX3, X = I, Br, and Cl) represent a particularly interesting example in this context. These layered materials consist of ferromagnetic planes of Cr3+: d3 cations arranged in a honeycomb lattice with edge-sharing octahedral coordination.<sup>6-9</sup> Bulk CrX<sub>3</sub> materials exist in two structural phases with different stacking sequences along the c axis: a lowtemperature rhombohedral structure and a high-temperature monoclinic structure. 8,10 Recently, it has been shown that the stacking pattern in CrX3 bilayers can give rise to a sign change in the interlayer magnetic coupling. 11-14 This stackingdependent interlayer magnetic exchange has been experimentally demonstrated in both CrI3 and CrBr3, with the monoclinic stacking supporting an antiferromagnetic (AFM) interlayer coupling, while the rhombohedral stacking supports a ferromagnetic (FM) coupling instead. 15-18 This result has important implications for the moiré physics: a small twisting in bilayers creates a long-period moiré pattern, in which the stacking order in each local region is similar to the corresponding lattice-matched stacking configuration. As such, the competing stacking-dependent interlayer interactions

can give rise to novel magnetic states upon twisting, as recently demonstrated for  ${\rm CrI_3.}^{19}$ 

In this Letter, we study the magnetic phases in twisted bilayer  $\text{CrX}_3$  spanning all three halide ions using a combination of *ab initio* calculations and atomistic simulations. We show that the interlayer exchange is mostly FM with three symmetry-related AFM patches. Noncollinear magnetic states, including skyrmion crystals, are obtained at small twist angles. These nontrivial phases arise from the competition between the interlayer AFM coupling in the monoclinic stacking regions of the moiré superlattice and the energy cost to form AFM–FM domain walls. Our results agree with recent magnetic circular dichroism (MCD) experiments in  $\text{CrI}_3^{19}$  and provide insights for the wealth of noncollinear magnetic phases that can potentially be obtained in twisted bilayer chromium trihalides.

We start by presenting the spin Hamiltonian that will enable the description of the magnetic properties of CrX<sub>3</sub> bilayers upon twisting

$$\mathcal{H} = \mathcal{H}_{\text{intra}}^{1} + \mathcal{H}_{\text{intra}}^{2} + \mathcal{H}_{\text{inter}}$$
 (1)

Received: May 27, 2021 Revised: July 23, 2021 Published: August 2, 2021





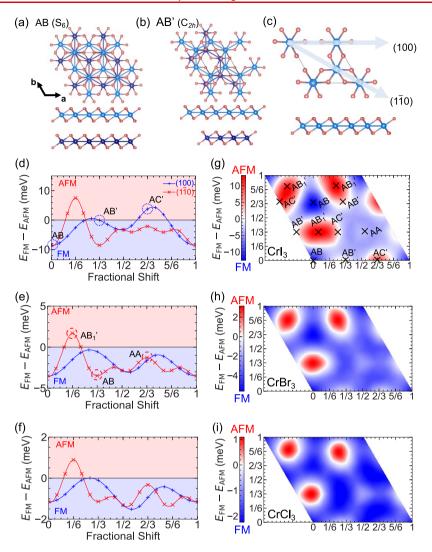


Figure 1. Top and side views of  $CrX_3$  bilayers are shown in panels a and b for rhombohedral (AB) and monoclinic (AB') stacking, respectively. The unit cells are outlined in both cases. The larger, light (dark) blue spheres represent the Cr atoms in the top (bottom) layer, while the smaller, red spheres represent the halide anions. (c)  $CrX_3$  monolayer unit cell (top and side view), where the high-symmetry lateral shift directions [100] and [110] are indicated by arrows. (d-f) Energy difference ( $E_{FM} - E_{AFM}$ ) for various stacking displacements along the high-symmetry directions (100) (blue) and (110) (red) for  $CrI_3$ ,  $CrBr_3$ , and  $CrCl_3$  bilayers, respectively. A positive energy difference denotes an AFM ground state, while a negative difference denotes a FM ground state. (g-i) Moiré field patterns calculated for  $CrI_3$ ,  $CrBr_3$ , and  $CrCl_3$  bilayers, respectively. The patterns are obtained by interpolating the data in panels d-f via fitting to a polynomial. Blue regions correspond to a FM interlayer coupling, while red regions correspond to an AFM interlayer coupling. Specific stacking sequences defined in the main text are labeled in panel g, and the corresponding lateral shifts are denoted in panels d and e. The Supporting Information offers further details.

where  $\mathcal{H}_{\text{intra}}^{1(2)}$  includes the symmetry-allowed intraplane exchange terms in layer 1 (2) and  $\mathcal{H}_{\text{inter}}$  incorporates the interlayer exchange

$$\mathcal{H}_{\text{intra}} = -\frac{J}{2} \sum_{i,\mu} \mathbf{S}_{i} \cdot \mathbf{S}_{i+\hat{\delta}_{\mu}} - \frac{\lambda}{2} \sum_{i,\mu} S_{i}^{z} S_{i+\hat{\delta}_{\mu}}^{z}$$
$$-\frac{D}{2} \sum_{i,\mu} \left[ \hat{d}_{\mu} \cdot (\mathbf{S}_{i} \times \mathbf{S}_{i+\hat{\delta}_{\mu}}) \right] - A_{s} \sum_{i} (S_{i}^{z})^{2}$$
(2)

$$\mathcal{H}_{inter} = -\sum_{\langle ij \rangle} J^{\perp}(\mathbf{r}_{ij}) \mathbf{S}_i^1 \cdot \mathbf{S}_j^2$$
(3)

Here, i is the site index, and  $\hat{\delta}_{\mu}$  are the three nearest neighbors (nn) on the honeycomb lattice. J is the intralayer Heisenberg exchange coupling;  $\lambda$  is the anisotropic exchange coupling; and  $A_s$  is the single-ion anisotropy.  $J^{\perp}(\mathbf{r}_{ij})$  represents the interlayer

exchange coupling, and  $\mathbf{r}_{ij}$  is the interlayer displacement. Estimates for all of these constants are obtained from first-principles calculations (see below). D is the Dzyaloshinskii–Moriya interaction (DMI) and is introduced in the atomistic simulations.

The derivation of  $J^{\perp}$  entails building the CrX<sub>3</sub> bilayers. Each bilayer is initially constructed using the rhombohedral stacking with a vacuum of 20 Å along the c axis. The bilayers are subsequently relaxed within a FM state via density functional theory (DFT), as implemented in the Vienna Ab initio Simulation Package (VASP)<sup>20</sup> using projector augmented wave pseudopotentials.<sup>21</sup> Different exchange—correlation functionals were attempted with both PBEsol<sup>22</sup> and the DFT-D3 scheme<sup>23</sup> (the latter including vdW interactions), giving an in-plane lattice parameter and interlayer distance that differ from experimental data by less than 1%. On the basis of this

agreement, we proceed using the PBEsol functional throughout (see the Supporting Information for further details).

For small twist angles, the stacking order at any local region in the moiré pattern can be obtained by translating one of the monolayer units in the rhombohedral reference cell by the vector  $\mathbf{r} = \eta \mathbf{a} + \nu \mathbf{b}$ , where  $\eta, \nu \in [0, 1]$  and  $\mathbf{a}$  and  $\mathbf{b}$  are the lattice vectors of the unit cell. We organize bilayer stacking sequences into two groups: symmetric stacking sequences (rhombohedral) denoted as AB, AA, and BA and asymmetric stacking sequences (monoclinic) denoted as AB', AB<sub>1</sub>', and AC'. All six of these stacking arrangements can be achieved from lateral shifts along two high-symmetry directions: (100) and ( $1\overline{10}$ ) (panels a—c of Figure 1).

The moiré field is extracted from the stacking-dependent interlayer interaction in these bilayers.  $^{11,13,14}J^{\perp}(\mathbf{r})$  in eq 3 for a given stacking is obtained as  $(E_{AFM} - E_{FM})/2|S|^2$ , with  $|S| = \frac{3}{2}$ . Here,  $E_{\rm FM}$  and  $E_{\rm AFM}$  refer to the DFT energies in a FM state and an A-type AFM state. For the magnetic calculations at different stackings, we have employed  $\widetilde{DFT}+U^{24}$  to treat the localized Cr 3d electrons with an on-site Coulomb repulsion U = 3 eV, consistent with previous literature, 11,12,25 and with constrained random phase approximation (cRPA) calculations on CrI<sub>3</sub><sup>26</sup> (see the Supporting Information for further details on the DFT+U calculations). The results for  $E_{\rm FM}-E_{\rm AFM}$  at different stackings for CrX3 bilayers are shown in panels d-i of Figure 1. As expected, the interlayer exchange modulates from FM to AFM as the stacking is changed; a dominant interlayer FM coupling is obtained with three symmetry-related AFM patches. For all halides, the rotationally symmetric AB, AA, and BA stacking sequences strongly favor a FM interlayer coupling. However, the broken symmetry stackings (AB', AB<sub>1</sub>', and AC') differ between the three compounds. In CrI<sub>3</sub>, an AFM coupling in all three stacking sequences is favored, while in CrBr3 and CrCl3, an AFM coupling is preferred only in the AB<sub>1</sub>' stacking sequence. Accordingly, a systematic reduction in the size of the AFM regions can be observed in panels g-i of Figure 1 as the size of the halide decreases. These findings agree with recent experimental 18,27 and theoretical work. 11,13,14,28 The sign change in the interlayer exchange can be understood from the competition between AFM nn  $t_{2g}\!-\!t_{2g}$  couplings and FM next-nn  $t_{2g}\!-\!e_g$  couplings. In the symmetric stacking sequences, the number of next-nn is greater than the number of nn, leading to an overall FM exchange, while for the asymmetric stacking sequences, the situation is reversed, leading to an AFM exchange. 11,29 First-principlesderived magnetic parameters in vdW magnets differ highly in the literature as a result of the use of different functionals and computational parameters.<sup>29</sup> We have employed a consistent methodology throughout to extract all couplings needed for the atomistic simulations (see the Supporting Information for more details).

To derive J,  $\lambda$ , and  $A_s$  from first principles, we follow a procedure analogous to that employed in ref 30 for monolayer  $CrI_3$ . Specifically, we consider four magnetic configurations in  $CrX_3$  monolayers: FM and AFM both oriented in plane (x) and out of plane (z). These calculations are performed using the same methodology described above for the bilayers within PBEsol+U (U=3 eV), including spin—orbit coupling (SOC) (see the Supporting Information for the energy mappings). The derived values of J,  $\lambda$ , and  $A_s$  are shown in Table 1. Importantly, we obtain J>0 (favoring FM interactions) in all materials with a value that decreases from I to Cl, as expected. The derived  $A_s>0$  favors an off-plane easy axis. For  $CrCl_3$ , this

Table 1. Magnetic Parameters Extracted from DFT Calculations in Monolayer CrX<sub>3</sub><sup>a</sup>

	$CrI_3$	CrBr <sub>3</sub>	CrCl <sub>3</sub>
J (meV)	4.06	3.42	2.37
$\lambda \; (\text{meV})$	0.14	0.04	0.003
$A_{\rm s}$ (meV)	0.03	0.03	0.006

 $^aJ$  is the intralayer symmetric Heisenberg exchange coupling;  $\lambda$  is the anisotropic exchange coupling; and  $A_s$  is the single ion anisotropy.

result disagrees with experiments; <sup>10</sup> therefore, dipole—dipole interactions have to be included to turn its anisotropy in plane (see the Supporting Information for further details).

We now employ the magnetic parameters derived above and further introduce the DMI for the atomistic simulations. We introduce the DMI in this manner because its first-principles derivation would entail noncollinear calculations beyond the monolayer (where DMI is not allowed by symmetry). Also, this allows us to easily probe changes upon tuning the DMI, something that could be attainable experimentally using different substrates or via liquid ion gating.<sup>31</sup> As such, we consider three different values of the DMI for each material: D/J = 0.05, 0.1, and 0.2. To find the ground state for the bilayer Hamiltonian (eq 1), we take the continuum limit and solve the Landau–Lifshitz–Gilbert (LLG) equation<sup>32</sup>

$$\frac{\mathrm{d}\mathbf{m}}{\mathrm{d}t} = -\gamma \mathbf{m} \times \mathbf{B}^{\mathrm{eff}} + \alpha \mathbf{m} \times \frac{\mathrm{d}\mathbf{m}}{\mathrm{d}t}$$
(4)

where  $\mathbf{m}$  is the magnetization,  $\mathbf{B}^{\text{eff}} = -\delta \mathcal{H}/\delta \mathbf{m}$ ,  $\gamma$  is the gyromagnetic ratio, and  $\alpha$  is the Gilbert damping coefficient. We solve the LLG equations for each layer self-consistently keeping  $|\mathbf{m}| = 1$  and imposing periodic boundary conditions. Our method is suitable to capture magnetic phases that are commensurate with the moiré superlattice<sup>4</sup> (see the Supporting Information for further details).

The main results for the magnetic phase diagrams at T=0 are summarized in Figures 2, 4, and 5 for  $CrI_3$ ,  $CrBr_3$ , and  $CrCl_3$ , respectively. A plethora of noncollinear phases, including skyrmion crystals (SkX), are obtained at small angles (or large moiré periods) driven by the competing magnetic interactions in the moiré superlattices. Reference 14 has also studied the magnetic phase diagrams of twisted trihalide bilayers, but the DMI was not considered, impeding the stabilization of SkX phases.

We start our discussion of the atomistic simulations with CrI3 bilayers that display the richest phase diagram as a function of the twist angle (panels a-c of Figure 2). For the smallest angles, a 1SkX/2SkX phase is the ground state (Figure 2d). This phase is stabilized when the moiré superlattice is large enough, so that one skyrmion forms in an AFM region on one layer, while two skyrmions form in the remaining two AFM patches on the other layer. For  $\theta > 0.72^{\circ}$ , a 1SkX/FM phase is obtained with a single skyrmion forming in the three overlapping AFM regions on one layer, while the other stays FM (Figure 2e). For even larger angles, a noncollinear 1 SkX/ spiral (Sp) phase is formed with a single skyrmion in one of the AFM patches on one layer and a spiral in the remaining two AFM regions on the other layer (Figure 2f). As the angle is increased further, a FM + tilted phase is obtained, in which the magnetization is out-of-plane in the FM background but acquires a finite in-plane component in the AFM regions (Figure 2g). The in-plane magnetization is opposite in the two layers, and its magnitude decreases with an increasing angle.

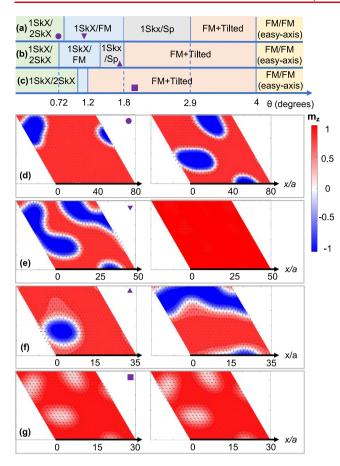


Figure 2. Phase diagram and magnetization textures of twisted bilayer CrI<sub>3</sub>. (a-c) Phase diagram of twisted bilayer CrI<sub>3</sub> as a function of twist angle  $\theta$  for different values of DMI. Here, panels a, b, and c correspond to D/J = 0.2, 0.1, and 0.05, respectively. (d) Magnetization texture of 1SkX/2SkX for D/I = 0.2 and  $\theta = 0.72^{\circ}$ . The 1SkX/ 2SkX phase competes in energy with a 3SkX/FM state, in which three skyrmions are formed on one layer, while the other remains FM. The 1SkX/2SkX phase has slightly lower energy than the 3SkX/FM phase because it minimizes the skyrmion-skyrmion interactions. However, this energy difference decreases for smaller  $\theta$  as the distance between the skyrmions becomes larger. (e) Magnetization texture of 1SkX/FM for D/J = 0.2 and  $\theta = 1.15^{\circ}$ . (f) Magnetization texture of 1SkX/Sp for D/J = 0.1 and  $\theta = 1.64^{\circ}$ . (g) Magnetization texture of FM + tilted state for D/J = 0.05 and  $\theta = 1.91^{\circ}$ . The x axis in panels d–g shows the real space position within the moiré unit cell of size  $L = a/2 \sin(\theta/2)$ , where a is the lattice spacing.

Finally, a transition from the FM + tilted phase to a FM/FM state is obtained at  $\theta \sim 4^{\circ}$ . This FM/FM phase is the ground state at large angles for all DMI strengths.

An analytical estimate for the critical twist angle to obtain a skyrmionic phase transition  $(\theta_c)$  can be derived considering the competition between domain wall energy formation and interlayer exchange energy. Considering a single AFM patch, flipping the magnetization in one of the layers would lower the interlayer exchange energy, producing an energy gain  $E_{\rm AFM} \sim 2f_{\rm AFM} \left(\frac{L}{a}\right)^2 \overline{J}^{\perp}$  (where  $f_{\rm AFM}$  is the area fraction of the AFM patch over the moiré unit cell,  $\overline{I}^{\perp}$  is the average AFM coupling, and a is the lattice spacing). This energy scales with the area of the AFM patch and, therefore, varies quadratically with the moiré period, L. On the other hand, this creates a domain wall with the rest of the system of length  $\delta \sim \pi (\left(J + \frac{\lambda}{2}\right)/(A_{\rm s} + \lambda + 0.72\overline{J}^{\perp}))^{1/2}a \text{ and energy cost}$   $E_{\rm DW} \sim \left(\frac{\pi}{a}\sqrt{\left(J + \frac{\lambda}{2}\right)(A_{\rm s} + \lambda + 0.72\overline{J}^{\perp})} - \frac{D\pi}{a}\right)L. \text{ Similar ex-}$ pressions are obtained in ref 19, but we also consider the contribution from the DMI (see the Supporting Information for more details). Importantly, for large enough L,  $E_{AFM}$  can overcome  $E_{\rm DW}$  and lead to a phase transition to a skyrmionic phase. The critical angle for the transition is determined by

$$\theta_{\rm c} \sim \frac{2f_{\rm AF}\overline{J}^{\perp}}{\pi \left(\sqrt{\left(J + \frac{\lambda}{2}\right)\left(A_{\rm s} + \lambda + 0.72\overline{J}^{\perp}\right)} - D\right)} \tag{5}$$

minimizing the energy.

This estimate is for a single domain and, therefore, only applicable when the AFM patches are well-separated. When the domain wall length  $\delta$  is comparable to the separation between AFM patches (as in CrI<sub>3</sub>; Figure 1g), there can be more complicated states. In any case, the analytical estimate in CrI<sub>3</sub> [ $\theta_c \sim 3^\circ$  (D/J = 0.2) and 2.3° (D/J = 0.1)] is in good agreement with our numerical results for the 1SkX/Sp to FM + tilted phase boundary [ $\theta_c \sim 2.9^\circ$  (D/J = 0.2) and 1.8° (D/J = 0.1)]. The trends are the expected ones as an increasing DMI decreases the domain wall energy and, therefore, increases  $\theta_c$ .

Our phase diagram is in agreement with recent experiments on  $CrI_3$  bilayers on hexagonal boron nitride (h-BN) substrates that demonstrated their high degree of magnetic tunability upon twisting, gating, and applied magnetic field using MCD. A FM/FM phase is indeed the ground state in these experiments for  $\theta > 3^\circ$ , while a noncollinear magnetic ground state arises at smaller angles, in agreement with our results. Because these MCD experiments are only sensitive to the z component of the magnetization, further work will be necessary to pinpoint the nature of this noncollinear magnetic phase and to check for the skyrmion phases that we predict.


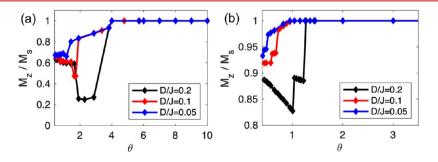


Figure 3. z component of the normalized average magnetization as a function of the twist angle ( $\theta$ ) for (a) CrI<sub>3</sub> and (b) CrBr<sub>3</sub> for varying D/J.

To make further connections with ref 19, we have also calculated the ratio of the z component of the normalized magnetization  $(M_z)$  and the saturation magnetization  $(M_s)$  for bilayer  ${\rm CrI}_3$  (Figure 3a). Experiments show that below  $\theta \sim 3^\circ$   $M_z/M_s$  drops gradually to a saturation value of  $\sim 0.6.^{19}$  Our simulations show a transition of the same nature taking place for  $\theta \sim 4^\circ$  with  $M_z$  slowly decreasing into the FM + tilted phase as the angle is lowered. For our lowest and intermediate DMIs (D/J=0.05 and 0.1), the magnetization decreases gradually into the different skyrmion phases, until it saturates at small angles to  $M_z/M_s \sim 0.65$ , close to the experimental value. For the largest DMI (D/J=0.2), the magnetization drops abruptly in the 1SkX/Sp phase instead, recovering the  $M_z/M_s \sim 0.65$  value at low angles. This abrupt drop has not been observed in experiments, suggesting that the DMI is smaller in bilayer  ${\rm CrI}_3$  on h-BN substrates.


Next, we discuss the phase diagram of CrBr<sub>3</sub>. The ground states are similar to those in CrI<sub>3</sub>, with FM/FM and 1SkX/2SkX phases emerging at large and small angles, respectively (panels a–d of Figure 4). At intermediate angles, 2SkX/FM (Figure 4e) and FM + tilted (Figure 4f) states are stabilized. The 2SkX/FM phase has two skyrmions on one layer along with a tilted FM on the third AFM patch. CrBr<sub>3</sub> satisfies the assumptions for the analytical estimate of the critical angle using eq 5 better than CrI<sub>3</sub> because the size of the AFM patches is smaller and they are well-separated (Figure 1h). This

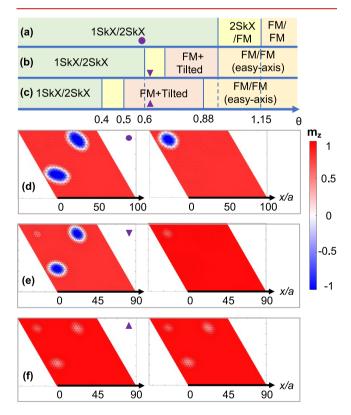

**Figure 4.** Phase diagram and magnetization textures in twisted bilayer CrBr<sub>3</sub>. (a–c) Phase diagram of twisted bilayer CrBr<sub>3</sub> as a function of the twist angle  $\theta$  for different values of DMI. Here, panels a, b, and c correspond to D/J=0.2, 0.1, and 0.05, respectively. (d) Magnetization texture of 1SkX/2SkX for D/J=0.2 and  $\theta=0.57^{\circ}$ . (e) Magnetization texture of 2SkX/FM for D/J=0.1 and  $\theta=0.64^{\circ}$ . (f) Magnetization texture of the FM + tilted state for D/J=0.05 and  $\theta=0.64^{\circ}$ . The x axis in panels d–f shows the real space position within the moiré unit cell.

estimate gives  $\theta_c$  for the skyrmionic phase transition  $\sim 0.5^{\circ}$ ,  $0.7^{\circ}$ , and  $1.4^{\circ}$  for D/J = 0.05, 0.1 and 0.2, respectively, consistent with the 2SkX/FM to FM/FM phase boundary that takes place at  $\theta_c \sim 0.5^{\circ}$ ,  $0.7^{\circ}$ , and  $1.15^{\circ}$ . Given the good agreement achieved between our  $M_z/M_c$  calculations and experimental data in  $CrI_3$ , we also calculate  $M_z/M_s$  for  $CrBr_3$ . The overall magnetization drop in this case is much less pronounced (different scale between left and right panels in Figure 3) because the AFM patches are smaller than in CrI<sub>3</sub>. The overall angle dependence remains similar for the different D/J values, with the magnetization dropping gradually for D/J= 0.05 and 0.1, while a more abrupt change is obtained for D/I= 0.2. At small angles, saturation is reached at  $M_z/M_s \sim 0.9$ 0.95. On the basis of our results, twisted bilayer CrBr<sub>3</sub> is a promising system to study because it should also display a rich phase diagram with nontrivial magnetic phases.

Finally, we discuss the phase diagram for CrCl<sub>3</sub> (panels a-c of Figure 5). Similar to CrI<sub>3</sub> and CrBr<sub>3</sub>, a FM/FM phase is the

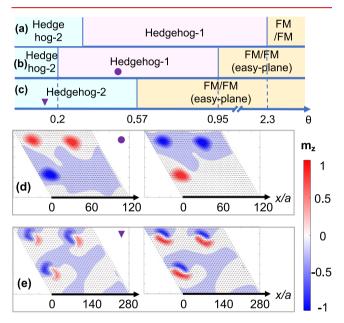

**Figure 5.** Phase diagram and magnetization textures of twisted bilayer  $CrCl_3$ . (a-c) Phase diagram of twisted bilayer  $CrCl_3$  as a function of the twist angle  $\theta$  for different values of the DMI. Here, panels a, b, and c correspond to D/J=0.2, 0.1, and 0.05, respectively. (d) Magnetization texture of Hedgehog-1 for D/J=0.1 and  $\theta=0.48^\circ$ . (e) Magnetization texture of Hedgehog-2 for D/J=0.05 and  $\theta=0.2^\circ$ . The x axis in panels d and e shows the real space position within the moiré unit cell.

ground state for large angles, with the distinction that, in this case, the magnetization is in-plane, which prevents SkX formation at small angles. Instead, two noncollinear magnetic orders arise, labeled as Hedgehog-1 and Hedgehog-2 (panels d and e of Figure 5), in which the in-plane magnetization acquires an out-of-plane component around the AFM patches that is opposite in the two layers. Hedgehog-1 resembles a meron configuration as the magnetization points up (or down) at the cores and in plane at the edges. However, unlike merons (or antimerons), the magnetization does not wind at the edges and, therefore, does not have a half-integer quantized topological charge. The Hedgehog-2 configuration has similar features, with a single AFM patch resembling a meron—antimeron pair. However, it also does not have the proper in-

plane winding of the spins and, therefore, does not have a quantized topological charge. The topological charge distribution of these two phases is presented in the Supporting Information.

In conclusion, we have shown that the interplay of the stacking-dependent interlayer exchange, twist angle, and DMI can lead to noncollinear magnetic states in bilayer chromium trihalides. In particular, we demonstrate that for small twist angles various skyrmion crystal phases can be stabilized in both CrI<sub>3</sub> and CrBr<sub>3</sub>, whereas for large angles all three systems are ferromagnetic. While we have focused here on homobilayer chromium trihalides, our approach provides a general framework for understanding chiral magnetism in twisted 2D magnets. Interesting directions for future work include the effects of gating and external magnetic field as well as the study of heterobilayers (CrX<sub>3</sub>/CrX<sub>3</sub>') combining different halide ions. In this situation, the lattice mismatch will give rise to a moiré pattern even without twisting. The effects of strain <sup>33,34</sup> and interlayer separation <sup>12</sup> are also interesting paths to explore.

#### ASSOCIATED CONTENT

# Supporting Information

The Supporting Information is available free of charge at https://pubs.acs.org/doi/10.1021/acs.nanolett.1c02096.

Structural parameters, comparison of exchange—correlation functionals, magnetic shape anisotropy, continuum free energy, topological charge density of CrCl<sub>3</sub>, domain wall energy, and critical angle estimation (PDF)

#### AUTHOR INFORMATION

### **Corresponding Authors**

Onur Erten — Department of Physics, Arizona State University, Tempe, Arizona 85287, United States; orcid.org/0000-0002-1944-239X; Email: onur.erten@asu.edu

Antia S. Botana — Department of Physics, Arizona State University, Tempe, Arizona 85287, United States; Email: antia.botana@asu.edu

# **Authors**

**Muhammad Akram** – Department of Physics, Arizona State University, Tempe, Arizona 85287, United States

Harrison LaBollita – Department of Physics, Arizona State University, Tempe, Arizona 85287, United States

Dibyendu Dey – Department of Physics, Arizona State University, Tempe, Arizona 85287, United States; orcid.org/0000-0002-2639-3266

Jesse Kapeghian – Department of Physics, Arizona State University, Tempe, Arizona 85287, United States

Complete contact information is available at: https://pubs.acs.org/10.1021/acs.nanolett.1c02096

## **Author Contributions**

<sup>†</sup>Muhammad Akram and Harrison LaBollita contributed equally to this work.

#### Notes

The authors declare no competing financial interest.

# ■ ACKNOWLEDGMENTS

The authors thank Nikhil Sivadas for sharing the data published in ref 11 with us. Jesse Kapeghian, Onur Erten, and Antia S. Botana acknowledge support from the National Science Foundation Award DMR 1904716. Muhammad Akram is supported by a Fulbright Scholarship. The authors acknowledge the Arizona State University (ASU) Research Computing Center for high-performance computing (HPC) resources.

#### REFERENCES

- (1) Cao, Y.; Fatemi, V.; Fang, S.; Watanabe, K.; Taniguchi, T.; Kaxiras, E.; Jarillo-Herrero, P. Unconventional superconductivity in magic-angle graphene superlattices. *Nature* **2018**, *556*, 43–50.
- (2) Tong, Q.; Liu, F.; Xiao, J.; Yao, W. Skyrmions in the moiré of van der Waals 2D Magnets. *Nano Lett.* 2018, 18, 7194–7199.
- (3) Hejazi, K.; Luo, Ž.-X.; Balents, L. Noncollinear phases in moiré magnets. *Proc. Natl. Acad. Sci. U. S. A.* **2020**, *117*, 10721–10726.
- (4) Hejazi, K.; Luo, Z.-X.; Balents, L. Heterobilayer moiré magnets: Moiré skyrmions and the commensurate-incommensurate transition. *arXiv.org, e-Print Arch., Condens. Matter* **2021**, arXiv:2009.00860v2 https://arxiv.org/abs/2009.00860v2.
- (5) Akram, M.; Erten, O. Skyrmions in twisted van der Waals magnets. *Phys. Rev. B: Condens. Matter Mater. Phys.* **2021**, 103, L140406.
- (6) Handy, L. L.; Gregory, N. W. Structural properties of chromium(III) iodide and some chromium(III) mixed halides. *J. Am. Chem. Soc.* **1952**, *74*, 891–893.
- (7) Morosin, B.; Narath, A. X-Ray diffraction and nuclear quadrupole resonance studies of chromium trichloride. *J. Chem. Phys.* **1964**, *40*, 1958–1967.
- (8) McGuire, M. A.; Dixit, H.; Cooper, V. R.; Sales, B. C. Coupling of crystal structure and magnetism in the layered, ferromagnetic insulator CrI<sub>3</sub>. *Chem. Mater.* **2015**, *27*, 612–620.
- (9) Blei, M.; Lado, J. L.; Song, Q.; Dey, D.; Erten, O.; Pardo, V.; Comin, R.; Tongay, S.; Botana, A. S. Synthesis, engineering, and theory of 2D van der Waals magnets. *Appl. Phys. Rev.* **2021**, *8*, 021301.
- (10) McGuire, M. Crystal and magnetic structures in layered, transition metal dihalides and trihalides. *Crystals* **2017**, *7*, 121.
- (11) Sivadas, N.; Okamoto, S.; Xu, X.; Fennie, C. J.; Xiao, D. Stacking-dependent magnetism in bilayer CrI<sub>3</sub>. *Nano Lett.* **2018**, *18*, 7658–7664.
- (12) Klein, D. R.; MacNeill, D.; Song, Q.; Larson, D. T.; Fang, S.; Xu, M.; Ribeiro, R. A.; Canfield, P. C.; Kaxiras, E.; Comin, R.; Jarillo-Herrero, P. Enhancement of interlayer exchange in an ultrathin two-dimensional magnet. *Nat. Phys.* **2019**, *15*, 1255–1260.
- (13) Gibertini, M. Magnetism and stability of all primitive stacking patterns in bilayer chromium trihalides. *J. Phys. D: Appl. Phys.* **2021**, *54*, 064002.
- (14) Xiao, F.; Chen, K.; Tong, Q. Magnetization textures in twisted bilayer CrX<sub>3</sub> (X = Br, I). *Phys. Rev. Research* **2021**, *3*, 013027.
- (15) Huang, B.; Clark, G.; Navarro-Moratalla, E.; Klein, D. R.; Cheng, R.; Seyler, K. L.; Zhong, D.; Schmidgall, E.; McGuire, M. A.; Cobden, D. H.; Yao, W.; Xiao, D.; Jarillo-Herrero, P.; Xu, X. Layer-dependent ferromagnetism in a van der Waals crystal down to the monolayer limit. *Nature* **2017**, *546*, 270–273.
- (16) Li, T.; Jiang, S.; Sivadas, N.; Wang, Z.; Xu, Y.; Weber, D.; Goldberger, J. E.; Watanabe, K.; Taniguchi, T.; Fennie, C. J.; Fai Mak, K.; Shan, J. Pressure-controlled interlayer magnetism in atomically thin CrI<sub>3</sub>. *Nat. Mater.* **2019**, *18*, 1303–1308.
- (17) Song, T.; Fei, Z.; Yankowitz, M.; Lin, Z.; Jiang, Q.; Hwangbo, K.; Zhang, Q.; Sun, B.; Taniguchi, T.; Watanabe, K.; McGuire, M. A.; Graf, D.; Cao, T.; Chu, J.-H.; Cobden, D. H.; Dean, C. R.; Xiao, D.; Xu, X. Switching 2D magnetic states via pressure tuning of layer stacking. *Nat. Mater.* **2019**, *18*, 1298–1302.
- (18) Chen, W.; Sun, Z.; Wang, Z.; Gu, L.; Xu, X.; Wu, S.; Gao, C. Direct observation of van der Waals stacking-dependent interlayer magnetism. *Science* **2019**, *366*, 983–987.
- (19) Xu, Y.; Ray, A.; Shao, Y.-T.; Jiang, S.; Weber, D.; Goldberger, J. E.; Watanabe, K.; Taniguchi, T.; Muller, D. A.; Mak, K. F.; Shan, J. Emergence of a noncollinear magnetic state in twisted bilayer CrI<sub>3</sub>.

- arXiv.org, e-Print Arch., Condens. Matter 2021, arXiv:2103.09850 https://arxiv.org/abs/2103.09850.
- (20) Kresse, G.; Furthmüller, J. Efficient iterative schemes for ab initio total-energy calculations using a plane-wave basis set. *Phys. Rev. B: Condens. Matter Mater. Phys.* **1996**, 54, 11169–11186.
- (21) Blöchl, P. E. Projector augmented-wave method. *Phys. Rev. B: Condens. Matter Mater. Phys.* **1994**, *50*, 17953–17979.
- (22) Perdew, J. P.; Ruzsinszky, A.; Csonka, G. I.; Vydrov, O. A.; Scuseria, G. E.; Constantin, L. A.; Zhou, X.; Burke, K. Restoring the density-gradient expansion for exchange in solids and surfaces. *Phys. Rev. Lett.* **2008**, *100*, 136406.
- (23) Grimme, S.; Antony, J.; Ehrlich, S.; Krieg, H. A consistent and accurate ab initio parametrization of density functional dispersion correction (DFT-D) for the 94 elements H-Pu. *J. Chem. Phys.* **2010**, 132, 154104.
- (24) Liechtenstein, A. I.; Anisimov, V. I.; Zaanen, J. Density-functional theory and strong interactions: Orbital ordering in Mott-Hubbard insulators. *Phys. Rev. B: Condens. Matter Mater. Phys.* **1995**, 52, R5467–R5470.
- (25) Lu, X.; Fei, R.; Zhu, L.; Yang, L. Meron-like topological spin defects in monolayer CrCl<sub>3</sub>. Nat. Commun. 2020, 11, 4724.
- (26) Jang, S. W.; Jeong, M. Y.; Yoon, H.; Ryee, S.; Han, M. J. Microscopic understanding of magnetic interactions in bilayer CrI<sub>3</sub>. *Phys. Rev. Materials* **2019**, *3*, 031001.
- (27) Kim, H. H.; Yang, B.; Li, S.; Jiang, S.; Jin, C.; Tao, Z.; Nichols, G.; Sfigakis, F.; Zhong, S.; Li, C.; Tian, S.; Cory, D. G.; Miao, G.-X.; Shan, J.; Mak, K. F.; Lei, H.; Sun, K.; Zhao, L.; Tsen, A. W. Evolution of interlayer and intralayer magnetism in three atomically thin chromium trihalides. *Proc. Natl. Acad. Sci. U. S. A.* **2019**, *116*, 11131–11136.
- (28) Soriano, D.; Cardoso, C.; Fernández-Rossier, J. Interplay between interlayer exchange and stacking in CrI<sub>3</sub> bilayers. *Solid State Commun.* **2019**, 299, 113662.
- (29) Soriano, D.; Katsnelson, M. I.; Fernández-Rossier, J. Magnetic two-Dimensional chromium trihalides: A theoretical perspective. *Nano Lett.* **2020**, *20*, *6225–6234*.
- (30) Lado, J. L.; Fernández-Rossier, J. On the origin of magnetic anisotropy in two dimensional CrI<sub>3</sub>. 2D Mater. **2017**, *4*, 035002.
- (31) Herrera Diez, L.; Liu, Y. T.; Gilbert, D. A.; Belmeguenai, M.; Vogel, J.; Pizzini, S.; Martinez, E.; Lamperti, A.; Mohammedi, J. B.; Laborieux, A.; Roussigné, Y.; Grutter, A. J.; Arenholtz, E.; Quarterman, P.; Maranville, B.; Ono, S.; Hadri, M. S. E.; Tolley, R.; Fullerton, E. E.; Sanchez-Tejerina, L.; Stashkevich, A.; Chérif, S. M.; Kent, A. D.; Querlioz, D.; Langer, J.; Ocker, B.; Ravelosona, D. Nonvolatile Ionic Modification of the Dzyaloshinskii-Moriya Interaction. *Phys. Rev. Appl.* **2019**, *12*, 034005.
- (32) Gilbert, T. L. A phenomenological theory of damping in ferromagnetic materials. *IEEE Trans. Magn.* **2004**, *40*, 3443–3449.
- (33) Webster, L.; Yan, J.-A. Strain-tunable magnetic anisotropy in monolayer CrCl<sub>3</sub>, CrBr<sub>3</sub>, and CrI<sub>3</sub>. *Phys. Rev. B: Condens. Matter Mater. Phys.* **2018**, 98, 144411.
- (34) León, A. M.; González, J. W.; Mejía-López, J.; de Lima, F. C.; Morell, E. S. Strain-induced phase transition in CrI<sub>3</sub> bilayers. 2D *Mater.* **2020**, *7*, 035008.