

Measuring the impact of spin-triplet exciton orientation on photocurrent in an organic transistor

Submitting to: Journal of Materials Chemistry C (EI)

Emily Bittle¹, Sebastian Engmann^{1,2}, Karl Thorley³, John Anthony³

Abstract: The dynamics of triplet and singlet exciton populations in organic semiconductors offer interesting possibilities in improving optical device efficiency, while also attracting interest for future applications as manipulatable states for quantum-state based computing. For technological applications, transduction of the exciton state is essential, thus detailed information on how the exciton dynamics affect device outputs is required. In this study, we measure the magnetic field response of the photocurrent in organic transistors to investigate the electrical signal resulting from singlet-triplet exciton dynamics. We find that controlling the orientation of the magnetic dipole orientation of the triplet by varying both the magnitude and orientation of the magnetic field with respect to single crystal axes in *anti*-2,8-difluoro-5,11-bis(triethylsilylethynyl)anthradithiophene (*adi*F TES ADT), allows us to manipulate the amount of current detected as a result of singlet fission.

¹Nanoscale Device Characterization Division, National Institute of Standards and Technology, 101 Bureau Drive, Gaithersburg, Maryland, 20899, United States

²Theiss Research, La Jolla, California 92037, United States

³Department of Chemistry, University of Kentucky, Lexington, Kentucky 40506, USA

1 Organic semiconductors support long lived excitons at room temperature due to a high binding
2 energy resulting from the low dielectric constant in these materials¹. In certain organic
3 semiconductors optically-excited singlet-state excitons can spontaneously decay to the triplet
4 state. In the process of singlet fission, a singlet exciton produces two triplet excitons. Triplet
5 excitons then have a prolonged lifetime due to their spin-forbidden transition to the ground state
6 and can live for microseconds². Spontaneous singlet fission/triplet fusion has been studied for
7 many years in organic materials and has gained attention as a way to increase efficiency in
8 organic light emitting diodes (LEDs) and photovoltaics.³ While singlet fission can be observed in
9 ultrafast optical⁴ and electron spin resonance experiments⁵, quantifying the impact of this process
10 on devices is complicated by electrical interfaces, electrostatics, and slow response of the device
11 when compared to exciton lifetimes. For example, “low voltage turn-on” has been suggested as a
12 signature of triplet fusion driving device enhancement in OLEDs^{6–10}, though we recently have
13 shown that the heterojunction band-offset in OLEDs is likely to drive this behavior.¹¹ This leads
14 to further questions about the impact that spontaneous fission/fusion has on the enhancement of
15 devices. Therefore, device based experiments are required to develop better diagnostics of the
16 impact of exciton processes on device performance.

17 In addition to the improvement of traditional devices, unique exciton states are being
18 investigated for their possible use in future computing paradigms.^{12,13} Especially enticing are
19 ways to move complex novel computing from low temperature into room temperature systems.
20 This requires the relevant quantum state to have a larger energy than the surrounding
21 environment. Excitons in organic semiconductors routinely have binding energies that are well
22 above $k_B T$ at room temperature³ resulting in longer lifetimes compared with traditional inorganic
23 excitons, and singlet fission/triplet fusion demonstrate unique processes that can be used to
24 manipulate available exciton states^{14,15}. The control of singlet and triplet populations made
25 possible through spontaneous singlet fission via a coherent triplet pair state can be exploited for
26 applications in magnetic field sensing or can be further refined to produce quantum states useful
27 for calculation.

28 Our previous study of magneto-photocurrent in tetracene showed that there is a dependence of
29 the magnetic field response depending on the in-plane orientation of the tetracene crystal with
30 respect to the magnetic field.¹⁶ In this study, we refine the measurement and calculation and

1 apply the technique to single crystals of *anti*- 2,8-difluoro-5,11-
2 bis(triethylsilylethynyl)anthradithiophene (*adiF* TES ADT)¹⁷. In tetracene crystals, the
3 herringbone molecular configuration puts molecules, and thereby magnetic axes, at nearly
4 perpendicular arrangement on the flat plane of the crystal. Molecules in *adiF* TES ADT crystals
5 arrange relatively parallel in the large area *ab* plane¹⁸ which will also align the magnetic dipoles
6 of neighboring molecules in the crystal.

7 We look at the impact that singlet fission has on the output current of a transistor in a magnetic
8 field as a function of crystal orientation. We correlate changes in the magnetic field response of
9 the photocurrent with crystal orientation to calculations of singlet fission based on a simple spin
10 Hamiltonian. From this, we gain insight into the steady state population density changes of
11 singlet and triplet states. The result reflects the spin character of the triplets formed by singlet
12 fission and is highly influenced by the zero-field splitting caused by the magnetic dipole-dipole
13 interaction within the triplet exciton for fields in the range of 0 mT to 200 mT. Using the
14 transistor as an electrical probe of the exciton population shows the possibility to transduce
15 exciton signal into solid state electrical systems and allows for single-crystal device studies
16 which provide a platform for understanding physics in ordered systems¹⁹ and exploiting
17 anisotropic effects²⁰.

Experimental:

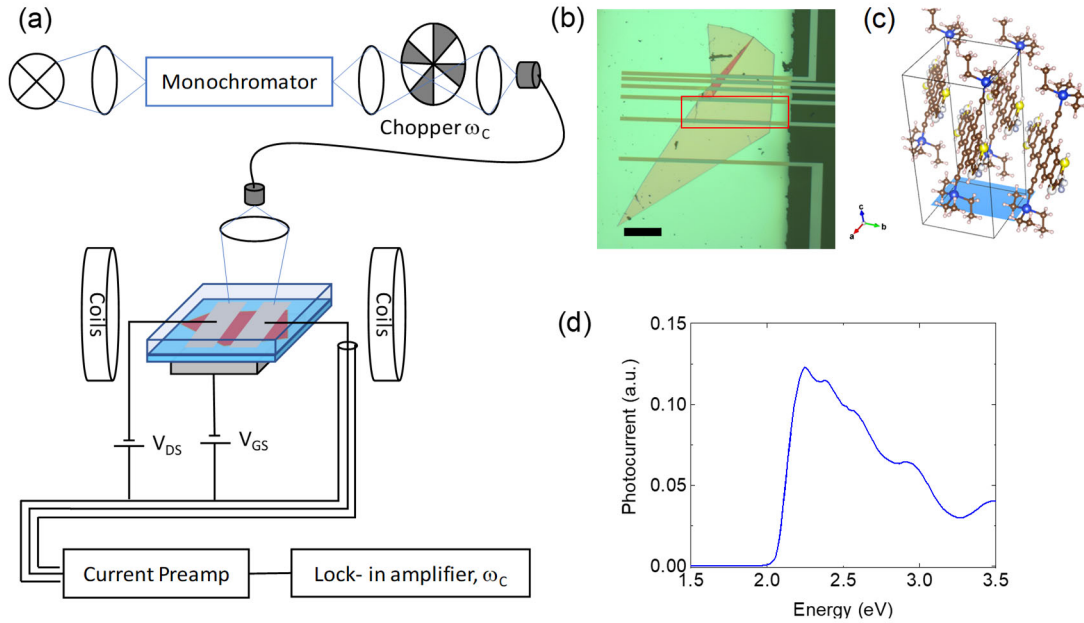


Figure 1: (a) Diagram of the measurement. The sample was placed between the coils of an electromagnet and was illuminated with light from a monochromator (blue lines follow the path of the light). Signal was measured at chopping frequency $\omega_c = 327$ Hz. (b) Micrograph of the sample used for the main paper. The pinkish-orange shape is a single crystal of *adiF* TES ADT. The yellow area is the gate metal and horizontal darker yellow thin lines are drain/_and-source contacts with varying distances. The 50 μm long channel ~~width~~ was used for MPC measurements, outlined by the red box, drain and source contacts are indicated by the red arrows. Black scale bar shows 100 μm . (c) Structure of *adiF* TES ADT^{21,22}. The drain-source plane of the crystal in the measured transistor lies near the *ab* plane.¹⁸ (d) Photocurrent spectrum of *adiF* TES ADT with no magnetic field, gate-source voltage set to -10 V and drain-source voltage set to -1 V.

A simplified representation of the measurement set-up is shown in Figure 1a. Transistors were made in top gate bottom contact configuration on quartz substrates to allow optical access from the bottom of the sample, the transistor used for this study is shown in Figure 1b. Drain and source contacts are masked using optical lithography; Au or Pd was thermally evaporated and

1 treated to produce a self-assembled monolayer of pentafluorobenzenethiol to improve contact
2 resistance.²³ Semiconductor crystals were grown using physical vapor growth^{24,25} in quartz tubes,
3 with the source material temperature at 160 °C, argon gas flow at 80 cm³ 60 s⁻¹ for seven days to
4 achieve crystals $\approx$ 0.5 mm on a side in the *ab*-plane. Crystals were hand positioned using a hair
5 from a synthetic paint brush and electrostatically held to the sample substrate and contacts.
6 Polymer dielectric Teflon was applied using spin coating (at 500 ($2\pi/60$) rad s⁻¹ for 5 s and
7 3000 ($2\pi/60$) rad s⁻¹ for 45 s), dried for 2 h in a nitrogen purge box and then further dried
8 overnight in vacuum at room temperature. Teflon AF 2400 was dissolved in a 25 mg/mL
9 solution with Fluorinert FC-40 at 60 °C for five days before coating.²⁶ Capacitance per area C/A
10 $= 1.15 \times 10^{-4}$ F/m² was measured, which corresponds to approximate dielectric thickness of 150
11 nm. Aluminum was used as the gate metal and was evaporated through a shadow mask. Current-
12 voltage characteristics of the transistor used to produce data in the main text are shown in
13 Supplementary Material, figure S1.

14 The sample is illuminated through the glass substrate with monochromatic light chopped at 327
15 Hz. The transistor gate and drain are held at constant bias using two matching battery sources
16 with common ground. Photocurrent through the source contact is measured through a
17 preamplifier set to 1 μ A/V with a 6 dB bandpass filter set to cutoff at 3 Hz and 3 kHz. The signal
18 is processed using a lock-in amplifier set to the optical chopper frequency with time constant at
19 300 ms. To obtain magnetic field dependence of the photocurrent, an electromagnet is used to
20 incrementally step the magnetic field, which is measured between the poles using a Hall bar
21 sensor with 7.78×10^{-2} V/T sensitivity. The sample is mounted on a manual rotation stage with
22 1-degree accuracy to facilitate angle dependent measurements. The measurement is performed in
23 a nitrogen purged glovebox.

24 Photocurrent at zero applied magnetic field as a function of wavelength is shown in figure ~~1e~~1d
25 and agrees well with a previous study of photocurrent in diF TES ADT.²⁷ For measurements of
26 photocurrent, the gate source voltage (V_{GS}) was set to -10 V and the drain-source voltage (V_{DS})
27 was set to -1 V (see Supplementary Material, figure S1). The photocurrent is zero below the
28 singlet excitation energy around 2.1 eV, indicating that the photocurrent originates from the
29 formation of a singlet exciton.

Results and Discussion:

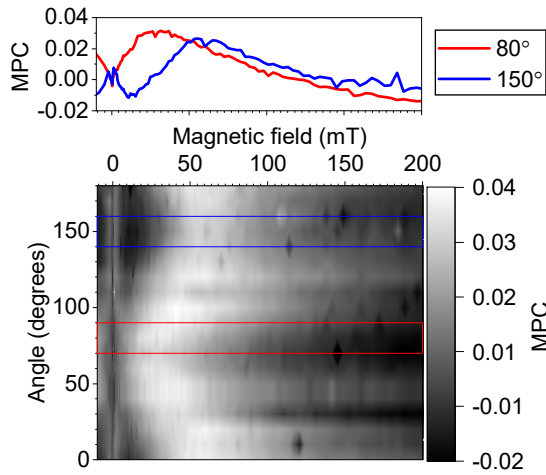


Figure 2: Magnetic field dependence of the photocurrent response in single crystal *adif* TES ADT transistor. The magnetic field runs approximately parallel to the *ab* crystal plane. Photocurrent was produced using 550 nm light.

To investigate spin dependent processes in the photocurrent (I_p) owing to the spontaneous formation of triplets, the magnetic field was scanned between -10 mT and 200 mT to measure the magnetic-field effects on the photocurrent (MPC). MPC is expressed as relative photocurrent defined with respect to the zero-field photocurrent, $MPC = [I_p(B) - I_p(B = 0 \text{ mT})] / I_p(B = 0 \text{ mT})$. The transistor was rotated from 0° to 180° in 10° steps. The magnetic field dependence of the photocurrent is shown in figure 2 and Supplementary Material figure S2 for a sample with Au contacts, and in figure S3 for a sample with Pd contacts. Similar signal was found for both samples (with crystals at different orientation with respect to the samples holder) suggesting that effects at the contacts do not contribute substantially to the signal. A broad peak can be observed shifting between 28 mT to 58 mT with orientation in the magnetic field. A narrow peak is seen below 10 mT at certain angles with a peak that shifts between 1.5 mT and 4 mT.

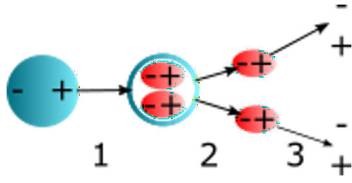


Figure 3: A simple diagram of singlet fission and triplet conversion to charges. In step 1, the singlet exciton (green, circle) spontaneously forms two bound triplet excitons (red, oval) with overall singlet character. In step 2 the triplet excitons separate into two independent quasi-particles which later decay into free charges (step 3).

To better understand the origin of the MPC, a simple model was used to calculate the photocurrent as a function of magnetic field amplitude and direction. A simple illustration of singlet fission to charge formation is shown in Figure 3. Due to the short lifetime and strong photoluminescence of the singlet state and relatively long lifetime and spin forbidden photoluminescence of the triplet²⁸, we assume that all singlet excitons will either decay to the ground state without contributing to the photocurrent or will go through singlet fission to form triplets which then decay to free charges. Triplet decay to charges can happen when the local electric field is high enough to overcome the binding energy, which is possible in transistors at the metal contact^{23,29}, due to gate field, or when interacting with radical or trap states.^{27,30–32}

We determine the density of triplet state excitons and resulting photocurrent through singlet fission using a model developed by Timmel et al.³³ that we previously applied to understand anisotropic MPC in tetracene.¹⁶ At steady state (relevant to our slow measurements at 327 Hz) the triplet population is

$$\Phi_T(B) = 1 - \sum_{m,n} |P_{mn}^S|^2 \frac{k^2}{k^2 + (\omega_m - \omega_n)^2} \quad \text{Equation 1}$$

The triplet-triplet pair states formed (m and n) by spontaneous singlet fission will match the spin character of the singlet state S, such that the quantum probability $P_{mn}^S = \langle m|S\rangle\langle S|n\rangle$, where $\langle S|m\rangle$ is the overlap in singlet and triplet-triplet pair states, will be non-zero. The energy of the triplet state is given by $E_l = \hbar\omega_l$ and we assume that the formation rate k has one value. The calculated magneto-photocurrent is proportional to the triplet density in a magnetic field normalized to the triplet density with no field:

$$MPC \propto \frac{\Phi_T(B) - \Phi_T(0)}{\Phi_T(0)} \quad \text{Equation 2}$$

The two interacting triplets were modelled using a simple spin Hamiltonian

$$H = \sum_{i=1}^2 (H_{Zi} + H_{Ti}) + H_{ex} \quad \text{Equation 3}$$

Where H_{Zi} is the Zeeman interaction

$$H_{Zi} = \mu_B g_i \vec{S}^i \cdot \vec{B} \quad \text{Equation 4}$$

μ_B is the Bohr magneton, the g-factor is set to 2, S^i is the spin operator of spin i , and B is the magnetic field. The zero-field splitting (H_{Ti}) due to unpaired spin interactions is given by

$$H_{Ti} = \frac{1}{3} D \left((S_z^i)^2 - S^i(S^i + 1) \right) + E \left((S_x^i)^2 + (S_y^i)^2 \right) \quad \text{Equation 5}$$

Where D and E are experimentally determined values of the zero field splitting parameters in the molecular crystal, which originate in the spin-spin interactions of charges within an exciton. When comparing the model to the single crystal data, an arbitrary offset is required as the orientation of the D/E frame is not regularly measured in experiments using polycrystalline samples^{28,34}. The exchange interaction for two spins i and j

$$H_{ex} = -J \left((\vec{S}^i \cdot \vec{S}^j) + 1/4 \right) \quad \text{Equation 6}$$

Where we have used $J \approx 1.24 \times 10^{-2} \mu\text{eV} (\ll D)$.³¹

To calculate the energy levels and eigenvalues of the nine triplet pair states, we use EasySpin written by Stoll and Schweiger³⁵ and solve for a system of two spin 1 particles. The relevant singlet state is derived from previous work³⁶ and we give a brief description here. A four-electron system will result in two states with overall spin $S = 0$. One is a combination of two singlet states and the other can be represented in the zero-field triplet state basis giving a spin allowed singlet state that has significant triplet character. This state, defined in the diagonalized zero-field triplet basis with the triplet states $|x\rangle$, $|y\rangle$ and $|z\rangle$, is given by

$$|S\rangle = \frac{1}{\sqrt{3}} (|x\rangle|x\rangle + |y\rangle|y\rangle + |z\rangle|z\rangle) \quad \text{Equation 7}$$

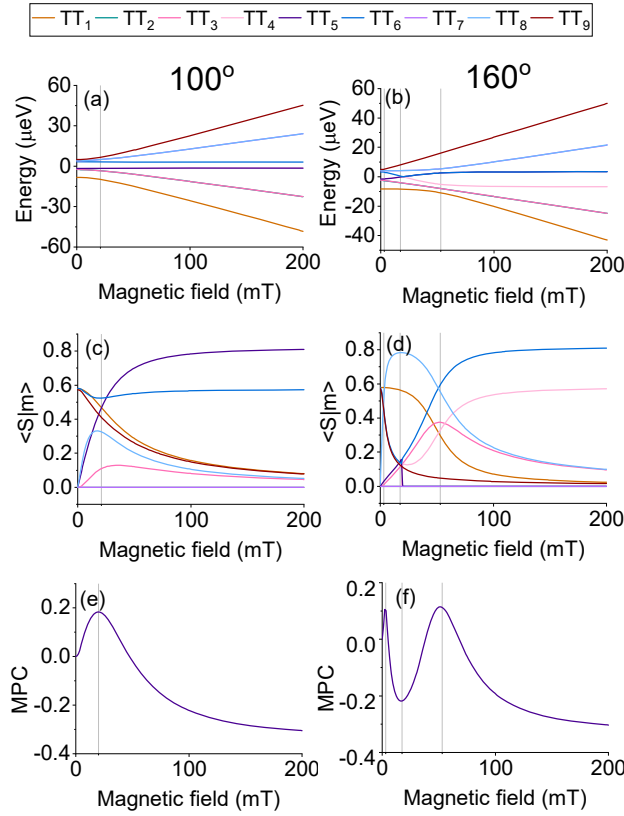


Figure 4 Results of calculation for triplet pair energy, singlet-triplet pair state overlap and magneto-photocurrent at 100° and 160°. Triplet levels are labelled from lowest to highest energy, with energy differences defined with respect to the $B = 0$ triplet energy without zero-field splitting. Grey lines indicate inflection points in the MPC. (a), (c), and (e) show 100°; (b), (d), and (f) show 160°, which are defined with respect to the magnetic axes as defined by the Hamiltonian given in Equation 3.

The triplet pair energy and eigenstate overlap with the singlet are both affected by the magnetic field, as shown in Figure 4 for two orientations of the crystal in the magnetic field. TT_i indicates the nine triplet-triplet pairs (eigenstates calculated from Equation (3)) and are ordered from $i = 0$ to $i = 9$ - from lowest to highest energy. The calculated MPC is also shown. So long as k is smaller than the energy difference, $k < \omega_m - \omega_n \approx 1 \text{ ns}^{-1}$, we get a result that agrees well with experiment.^{16,33} Peaks and valleys in the resulting MPC most closely follow the overall singlet character of the triplet states. As seen in Figure 4 (e), the one inflection point marked with a grey vertical line in the MPC occurs at a crossing point in the singlet character of the various TT states in (c). Similarly, the three inflection points in (f) correlate with crossover in singlet

character between TT states in Figure 4 (d). These crossover points coincide with avoided crossings in the energy spectrums Figure 4 (a) and (b).

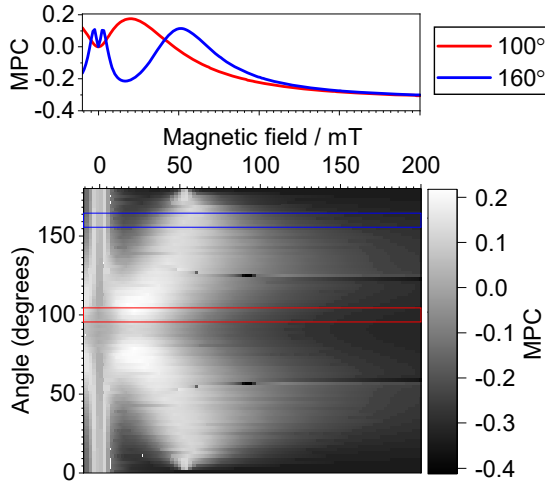


Figure 5 Results of the magneto-photocurrent calculation. The top graph shows line profiles of the average of regions marked in red and blue on the bottom graph centered at 100° and 160°. Avoided crossings in the energy levels produce sharp changes in the MPC, seen around 50° and 125° in the calculation. These sharp changes will not be observable in the reported experiment.

A plot of the results of the photocurrent calculation for magnetic field amplitude and direction is shown in Figure 5. The position of the peaks and valleys in the MPC with respect to magnetic field and orientation are affected by the values for D and E in the zero-field splitting term, as these values determine the energetic spread of the $B = 0$ T energies of the triplet-triplet states and therefore the magnetic field values of avoided crossings as energies change linearly as a result of the Zeeman effect (Equation (4)). In comparison to the experimental results shown in Figure 2, a best estimate gives $D = 6.2 \mu\text{eV}$ and $E = 0.4 \mu\text{eV}$. These values are in reasonable agreement to results from optically detected magneto-resonance measurements done on diF TES ADT: $D = 5.38 \mu\text{eV}$ and $E = 0.12 \mu\text{eV}$ ²⁸. It should be noted that the D and E values of the triplet state given here are measured in a crystal. With a phase transition near room temperature, diF TES ADT can exhibit multiple phases at room temperature³⁷ which may contribute to differences in the dipolar

interaction terms when comparing studies. Due to the geometry and processing of the device, we are not able to determine the exact crystal structure for the single crystal reported here.

For *adiF* TES ADT in the magnetic field range of 0 mT to 200 mT, we find that the qualitative shape of the magneto-photocurrent can be modelled by the spontaneous formation of triplet states from photogenerated singlet states. Depending on magnitude and orientation, we can control spontaneous fission and detect the resulting current in a device that is simple to fabricate. Matching the model and experiment, we get an approximately 75° offset between the device holder axes and the axes defined by the zero-field splitting parameters. Previous studies of magneto-electroluminescence have used hyperfine interactions between polaron pairs to describe behavior below 500 μ T.³⁸ As the fields measured here are well above the approximate local hyperfine fields for polarons, our results agree well with previous studies which do not take into account the hyperfine term.^{28,39} Photocurrent in single crystals of tetracene similarly shows a structured, anisotropic magnetic field response for fields 0 mT to 200 mT¹⁶ and between 200 mT and 500 mT⁴⁰ that can be well described by a model including the zero-field splitting of the triplet exciton.

Key differences between the modelled data and experiment may reflect the simplifications in the model where the device properties are not considered. For example, the magnitude of the resulting change in photocurrent is much larger in the model compared to experiment. This may be due to simplifying assumptions in which singlet excitons do not contribute to current, or to assumptions regarding the collection of charges from triplet states. We have built a device that supports majority hole transport using high work function drain and source contacts with a material that typically works as a p-type-like semiconductor. The result is that there are not efficient pathways for negative charges to escape the device. The free negative charges may then recombine with free holes, decreasing the carriers that can contribute to current in the device. Similarly, this effect may result in the positive offset of values in the experiment when compared to the model, as a lower triplet formation will also result in a smaller number of these free electrons formed. Furthermore, real device defect density and crystal structure affect both charge transport and exciton dynamics^{41,42}, resulting in changes to expected results. These cases illustrate the importance of device design in balancing competing effects that can decrease the

device enhancements predicted from ultra-fast optical measurements of exciton dynamics, and impact the accurate measurement of exciton population dynamics on devices.

The possibilities of using singlet-triplet exciton dynamic states for enhancement of device efficiency and computation have been driven by observations from ultra-fast optical measurements and electron spin resonance measurements. While these measurements show intriguing physics, current indicator measurements of the impact of triplet/singlet interconversion in devices do not easily, quantitatively, and unambiguously show the improvements made through synthesis of new molecules/polymers or through device design.¹¹ Unambiguously determining the effect of triplet/singlet interconversion in device measurements is difficult due to the slow response ($\approx$ MHz in diodes)⁴³ and size of devices (> 10 's nm) compared to exciton lifetimes (GHz) and diffusion lengths (< 10 's nm)¹. Further work on triplet/singlet exciton dynamics in organic semiconductor devices should therefore pursue an indicator ~~measurement metric~~ method which

- 1) Shows true indication of triplet enhanced performance of devices
- 2) Quantifies the changes in device performance that are due to singlet/triplet interconversion
- 3) Is easy to use to encourage universal acceptance

Developing an indicator metric will take coordination between device and ultra-fast physical measurements. ~~These measurement developments~~ metric would allow for the progressive development of materials and device structures that take advantage of singlet/triplet interconversion.

Conclusion:

In this paper, we demonstrate a relatively simple indicator measurement of changes to photocurrent signal when directly manipulating the triplet/singlet dynamics using a magnetic field. We've shown that the measurement and model presented here indicate singlet/triplet interconversion in *adiF* TES ADT. Our goal in future studies is to develop methods to quantify the impact of singlet/triplet exciton dynamics on completed device structures using the magnetic field response of devices.

Author Contributions:

E.G.B. designed the experiment, collected data, performed calculations, and wrote the manuscript. S.E. assisted in experiment design and calculations. K.T. and J. A. synthesized the *adiF* TES ADT. All authors reviewed and edited the final manuscript.

Conflicts of interest:

There are no conflicts to declare.

Acknowledgements:

The authors thank Elise Treat and David Rutter for assistance on experimental design. S.E. acknowledges support from the U.S. Department of Commerce, National Institute of Standards and Technology under the financial assistance award 70NANB17H305. JA and KT acknowledge support from the US National Science Foundation, under Cooperative Agreement No. 1849213. Certain commercial equipment, instruments, or materials are identified in this paper in order to specify the experimental procedure adequately. Such identification is not intended to imply recommendation or endorsement by the National Institute of Standards and Technology, nor is it intended to imply that the materials or equipment identified are necessarily the best available for the purpose.

References:

- 1 C. J. Bardeen, *Annu. Rev. Phys. Chem.*, 2014, **65**, 127–148.
- 2 A. B. Pun, A. Asadpoordarvish, E. Kumarasamy, M. J. Y. Tayebjee, D. Niesner, D. R. McCamey, S. N. Sanders, L. M. Campos and M. Y. Sfeir, *Nat. Chem.*, 2019, **11**, 821–828.
- 3 A. Köhler and H. Bässler, *Mater. Sci. Eng. R Reports*, 2009, **66**, 71–109.
- 4 C. D. Cruz, E. L. Chronister and C. J. Bardeen, *J. Chem. Phys.*, 2020, **153**, 234504.
- 5 L. R. Weiss, S. L. Bayliss, F. Kraffert, K. J. Thorley, J. E. Anthony, R. Bittl, R. H. Friend, A. Rao, N. C. Greenham and J. Behrends, *Nat. Phys.*, 2017, **13**, 176–181.
- 6 A. K. Pandey and J. M. Nunzi, *Appl. Phys. Lett.*, 2007, **90**, 263508.

- 1 7 S.-J. He and Z.-H. Lu, *J. Photonics Energy*, 2016, **6**, 036001.
- 2 8 C. Xiang, C. Peng, Y. Chen and F. So, *Small*, 2015, **11**, 5439–5443.
- 3 9 Q. Chen, W. Jia, L. Chen, D. Yuan, Y. Zou and Z. Xiong, *Sci. Rep.*, 2016, **6**, 1–9.
- 4 10 A. K. Pandey, *Sci. Rep.*, 2015, **5**, 1–6.
- 5 11 S. Engmann, A. J. Barito, E. G. Bittle, N. C. Giebink, L. J. Richter and D. J. Gundlach,
6 *Nat. Commun.*, 2019, **10**, 227.
- 7 12 N. Y. Kim and Y. Yamamoto, *Exciton-Polariton Quantum Simulators*, Springer, Cham,
8 2017.
- 9 13 C. J. Bardeen, *J. Chem. Phys.*, 2019, **151**, 124503.
- 10 14 J. J. Burdett and C. J. Bardeen, *J. Am. Chem. Soc.*, 2012, **134**, 8597–8607.
- 11 15 S. L. Bayliss, L. R. Weiss, A. Rao, R. H. Friend, A. D. Chepelianskii and N. C.
12 Greenham, *Phys. Rev. B*, 2016, **94**, 45204.
- 13 16 H. J. Jang, E. G. Bittle, Q. Zhang, A. J. Biacchi, C. A. Richter and D. J. Gundlach, *ACS*
14 *Nano*, 2019, **13**, 616–623.
- 15 17 P. J. Diemer, J. Hayes, E. Welchman, R. Hallani, S. J. Pookpanratana, C. A. Hacker, C. A.
16 Richter, J. E. Anthony, T. Thonhauser and O. D. Jurchescu, *Adv. Electron. Mater.*, 2017,
17 **3**, 1600294.
- 18 18 O. D. Jurchescu, S. Subramanian, R. J. Kline, S. D. Hudson, J. E. Anthony, T. N. Jackson
19 and D. J. Gundlach, *Chem. Mater.*, 2008, **20**, 6733–6737.
- 20 19 V. Podzorov, *MRS Bull.*, 2013, **38**, 15–24.
- 21 20 E. G. Bittle, A. J. Biacchi, L. A. Fredin, A. A. Herzing, T. C. Allison, A. R. Hight Walker
22 and D. J. Gundlach, *Commun. Phys.*, 2019, **2**, 29.
- 23 21 R. K. Hallani, K. J. Thorley, Y. Mei, S. R. Parkin, O. D. Jurchescu and J. E. Anthony,
24 *Adv. Funct. Mater.*, 2016, **26**, 2341–2348.
- 25 22 K. Momma and F. Izumi, *J. Appl. Crystallogr.*, 2011, **44**, 1272–1276.

- 1 23 M. Waldrip, O. D. O. D. Jurchescu, D. J. D. J. Gundlach and E. G. E. G. Bittle, *Adv.*
2 *Funct. Mater.*, 2020, **30**, 1904576.
- 3 24 R. . Laudise, C. Kloc, P. . Simpkins and T. Siegrist, *J. Cryst. Growth*, 1998, **187**, 449–454.
- 4 25 C. Kloc, P. G. Simpkins, T. Siegrist and R. A. Laudise, *J. Cryst. Growth*, 1997, **182**, 416–
5 427.
- 6 26 A. F. Paterson, A. D. Mottram, H. Faber, M. R. Niazi, Z. Fei, M. Heeney and T. D.
7 Anthopoulos, *Adv. Electron. Mater.*, 2019, **5**, 1800723.
- 8 27 K. Paudel, G. Giesbers, J. Van Schenck, J. E. Anthony and O. Ostroverkhova, *Org.*
9 *Electron.*, 2019, **67**, 311–319.
- 10 28 C. K. Yong, A. J. Musser, S. L. Bayliss, S. Lukman, H. Tamura, O. Bubnova, R. K.
11 Hallani, A. Meneau, R. Resel, M. Maruyama, S. Hotta, L. M. Herz, D. Beljonne, J. E.
12 Anthony, J. Clark and H. Sirringhaus, *Nat. Commun.*, 2017, **8**, 15953.
- 13 29 J. Day, A. D. Platt, S. Subramanian, J. E. Anthony and O. Ostroverkhova, *J. Appl. Phys.*,
14 2009, **105**, 103703.
- 15 30 B. T. Lim, J. Cho, K. H. Cheon, K. Shin and D. S. Chung, *Org. Electron.*, 2015, **18**, 113–
16 117.
- 17 31 R. E. Merrifield, *Pure Appl. Chem.*, 1971, **27**, 481–498.
- 18 32 C. Liewald, D. Reiser, C. Westermeier and B. Nickel, *Appl. Phys. Lett.*, 2016, **109**,
19 053301.
- 20 33 C. R. Timmel, U. Till, B. Brocklehurst, K. A. McLauchlan and P. J. Hore, *Mol. Phys.*,
21 1998, **95**, 71–89.
- 22 34 S. L. Bayliss, A. D. Chepelianskii, A. Sepe, B. J. Walker, B. Ehrler, M. J. Bruzek, J. E.
23 Anthony and N. C. Greenham, *Phys. Rev. Lett.*, 2014, **112**, 238701.
- 24 35 S. Stoll and A. Schweiger, *J. Magn. Reson.*, 2006, **178**, 42–55.
- 25 36 J. J. Burdett, G. B. Piland and C. J. Bardeen, *Chem. Phys. Lett.*, 2013, **585**, 1–10.
- 26 37 O. D. Jurchescu, D. A. Mourey, S. Subramanian, S. R. Parkin, B. M. Vogel, J. E.

Anthony, T. N. Jackson and D. J. Gundlach, *Phys. Rev. B - Condens. Matter Mater. Phys.*, 2009, **80**, 085201.

38 Z. Weng, W. P. Gillin and T. Kreouzis, Fitting the magnetoresponses of the OLED using polaron pair model to obtain spin-pair dynamics and local hyperfine fields, [extension://fa29bd03-24d6-419e-917b-daab7b8af701/enhanced-reader.html?openApp&pdf=https%3A%2F%2Fwww.nature.com%2Farticles%2Fs41598-020-73953-w.pdf](https://fa29bd03-24d6-419e-917b-daab7b8af701/enhanced-reader.html?openApp&pdf=https%3A%2F%2Fwww.nature.com%2Farticles%2Fs41598-020-73953-w.pdf), (accessed 19 May 2021).

39 G. B. Piland, J. J. Burdett, D. Kurunthu and C. J. Bardeen, *J. Phys. Chem. C*, 2013, **117**, 1224–1236.

40 N. E. Geacintov, M. Pope and S. Fox, *J. Phys. Chem. Solids*, 1970, **31**, 1375–1379.

41 P. Irkhin, I. Biaggio, T. Zimmerling, M. Döbeli and B. Batlogg, *Appl. Phys. Lett.*, 2016, **108**, 063302.

42 A. C. Jones, N. M. Kearns, J. J. Ho, J. T. Flach and M. T. Zanni, *Nat. Chem.*, 2020, **12**, 40–47.

43 L. C. C. Elliott, J. I. Basham, K. P. Pernstich, P. R. Shrestha, L. J. Richter, D. M. DeLongchamp and D. J. Gundlach, *Adv. Energy Mater.*, 2014, **4**, 1–8.