Heterogeneous Reaction Activities and Statistical Characteristics of Particle Cracking in Battery Electrodes



Downloaded via PURDUE UNIV on October 28, 2021 at 18:13:48 (UTC). See https://pubs.acs.org/sharingguidelines for options on how to legitimately share published articles.

Cite This: ACS Energy Lett. 2021, 6, 4065-4070



ACCESS

Metrics & More

Article Recommendations

si Supporting Information

The chemomechanical breakdown of electrodes can interrupt the stable operation of batteries. 1-4 Particle cracking can take place in nearly all electrode materials.^{3,5} In addition to the microstructural evolution of the active electrode, particle cracking can cause complex reactions with the electrolyte and instigate a rapid performance degradation.^{6,7} Chemomechanical properties have also become a focal point of research in solid-state batteries.8 Interested readers may refer to refs 3 and 9 to get more information about the negative impacts of chemomechanical breakdown. The chemomechanical breakdown is localized and dispersed heterogeneously in composite electrodes. Such complexity of mechanical damage is caused by the redox heterogeneity, which is also dependent on the local chemical environment. $^{10-15}$ For example, in a cathode of Li-ion batteries, crystal defects could cause geometrically non-optimal diffusion pathways at the single grain level (Figure 1a); 12,16 extended defects (e.g., grain boundaries and cracks)¹⁷ result in mesoscale charge heterogeneity in secondary particles that are thermodynamically stable and persist in a long-term operation (Figure 1b); 18,19 and the spatial arrangement of multiple phases in the composite electrode (active particles, inactive conductive additives, and micropores) further induces different degrees of electrochemical activities and particle utilization (Figure 1c).²⁰

Given the heterogeneous nature of the electrochemical activity and mechanical damage in electrodes, it is necessary to

Given the heterogeneous nature of the electrochemical activity and mechanical damage in electrodes, it is necessary to put forward a fundamental question: How do we count the statistical variation of the local events in the routine characterization of battery materials, thus being free of pitfalls and biased information?

put forward a fundamental question: How do we count the statistical variation of the local events in the routine characterization of battery materials, thus being free of pitfalls and biased information? The rapid development of analytical techniques has opened the door for precisely probing the dynamic process of mechanical degradation at different length scales. Here we elaborate the raised question in the context of a few state-of-the-art material characterization tools and their advantages and disadvantages, including electron microscopy and X-ray imaging techniques (Supporting Information).

The heterogeneous nature of electrochemical reactions and mechanical degradation places a daunting challenge in electron and X-ray characterizations.^{21–24} Recent large-scale electrode studies have uncovered that particle cracking is highly heterogeneous in composite electrodes. There are fundamental reasons and practical implications of such heterogeneity, which is ubiquitous even in the best-optimized commercial battery electrodes. 17,25-27 Figure 2 exemplifies such heterogeneity in a section of a practical electrode containing thousands of active particles. In a well-prepared academic electrode (Figure 2a), the degree of damage heterogeneity is overwhelmingly significant. Without a thorough investigation with specific attention paid to the statistics, we found that different biased conclusions could be made, as discussed below.

When we select only one particle to represent the damage level of this electrode, we found that one may draw conclusions all the way from no damage to severe damage. When we chose clusters of a few particles to present, we still observed a significant degree of variation between different clusters (Figure 2a). Although distinct degrees of damage are observed in these two selected clusters, they are only about 100 μ m apart in the electrode, highlighting a severely heterogeneous local chemistry. In secondary particles such as polycrystalline layered oxides, the internal crack patterns could be dramatically different from those observed on the external surface. The internal cracks can still be accessible to the electrolytic solution through open microcracks, thus contributing to the electrode-electrolyte reactions. Such reactions can be either beneficial or detrimental to the battery performance.

Received: September 30, 2021 Accepted: October 20, 2021



ACS Energy Letters http://pubs.acs.org/journal/aelccp Viewpoint

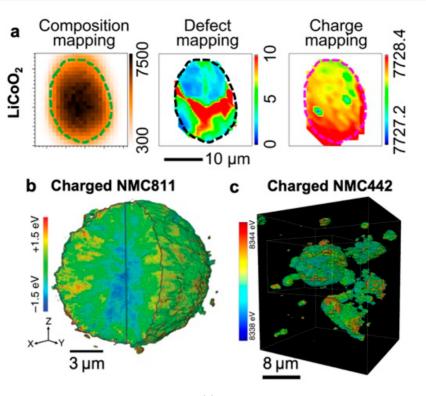


Figure 1. Heterogeneous reactions in the cathode of Li-ion batteries. (a) A LiCoO₂ single grain, where edge dislocations impact the charging reactions. The color code in the defect mapping represents the concentration of edge dislocations. The color code in the charge mapping represents the Co K-edge energy. Adapted with permission from ref 12. Copyright 2020 John Wiley & Sons, Inc. (b) Charged LiNi_{0.8}Mn_{0.1}Co_{0.1}O₂ (NMC811) secondary particle, where a highly heterogeneous shell-to-core charge propagation is observed. The color bar represents the relative Ni K-edge energy, where a higher value represents a higher state of charge. Reprinted from ref 19. Published open access, licensed under a Creative Commons Attribution 4.0 International License, by Springer-Nature 2020. (c) Charged LiNi_{0.4}Mn_{0.4}Co_{0.2}O₂ (NMC442) secondary particle ensembles. The color bar represents the Ni K-edge energy, where a higher value represents a higher state of charge. Reprinted from ref 20. Published open access, licensed under a Creative Commons Attribution 4.0 International License, by Springer-Nature 2018.

On one hand, cracks open up fresh surfaces to provide more ion intercalation sites, temporarily promoting reaction kinetics. On the other hand, these new surfaces may undergo surface reconstruction²⁸ to form densified interphase layers that impede the Li-ion diffusion in the long run. Therefore, the buried internal cracks play a significant role in affecting the battery performance. Moreover, these secondary particles could exhibit mesoscale pores, which could benefit reaction kinetics but are detrimental to the effective packing density. Without the capability of detecting the buried cracks and pores, the topographic imaging methods, e.g., top-view scanning electron microscopy (SEM), might miss some of the key information. Here we provide examples of particles with similar surface profiles but strikingly different internal cracking patterns (Figure 2b, with the surface renderings on the left and the corresponding virtual slices on the right). Next, we consider the reliability of the lab-based, focused ion beam (FIB)-prepared cross-section samples. FIB cross-sections have been widely applied to examine the internal structure of battery electrodes and solid electrolytes. Here we present the crosssections of the NMC electrode (Figure 2c) with selected particles of very different damage degrees enlarged in Figure 2d. Since we construct the cross-section from large-scale phase contrast X-ray tomography, we can show the cross-sections spanning a more extensive area compared to the standard SEM cross-sections reported in most studies.^{29,30} We observe a significant degree of variation between different cross-sections

of the same electrode. To increase statistical representativeness, we recommend that FIB cross-section be performed for a large area and over different depths.

In general, electrode preparation can greatly influence the chemomechanical response of battery particles during electrochemical cycling. Most commercial electrodes would undergo calendering³¹ before the cell manufacturing, which could cause residual stress on the particles and influence the subsequent chemomechanical characterization. Electrochemical cycling conditions, such as charging/discharging rate, temperature, voltage windows, and electrolytes, all critically affect the particle cracking behavior.^{3,5,32} We acknowledge that numerous other factors can influence the degree of heterogeneous chemomechanical breakdown. For example, whether a particle is hollow or solid at its pristine state³³ and how its primary crystal grains are spatially oriented³⁴ could both modulate the way that the mechanical strain is distributed, relaxed, and accumulated over time. The purpose of this Viewpoint is not to argue whether the heterogeneous damage of battery particles is caused by the experimental conditions. Instead, we would like to stress that, within the same electrode, different conclusions may be drawn based on different experimental protocols in the sample characterization if the statistical significance is not properly addressed. Advanced electrode manufacturing techniques, e.g., magnetic field directed assembly³⁵ and 3D printing,³⁶ could potentially produce well-structured electrodes with ordered particle

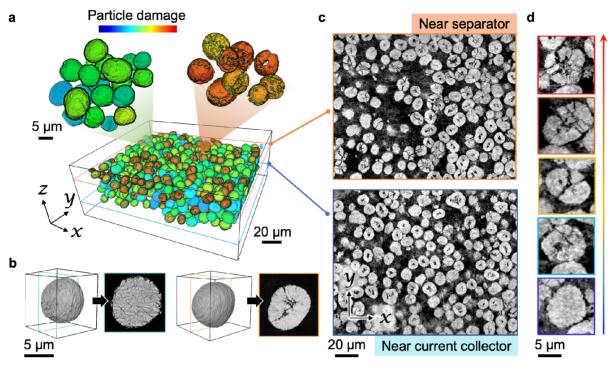


Figure 2. Heterogeneous particle damage in a well-formed NMC composite cathode. The particles in panel (a) are color-coded to their respective damage degrees. Two clusters with significant differences are enlarged for better visualization. Panel (b) shows two particles that demonstrate similar shapes when viewed from the exterior but exhibit very different internal structures, as revealed by their respective virtual 2D slices. Two distinct virtual slices at different depths over the same electrode are shown in panel (c). Panel (d) shows a few selected particles within the imaged electrode, demonstrating various degrees of particle cracking.

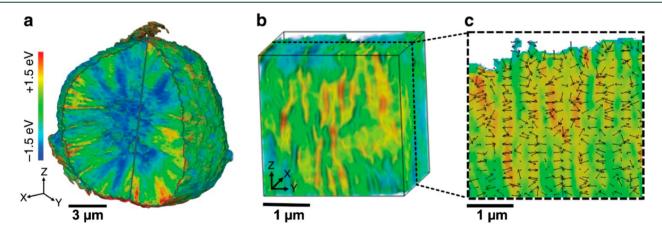


Figure 3. Surface and bulk redox heterogeneity in NMC particles. Panels (a) is a 3D visualization of the Ni redox heterogeneity within a NMC particle with radially aligned primary grains. Panels (b) and (c) are the 3D and 2D views of a sub-particle region from panel (a). Reprinted from ref 19. Published open access, licensed under a Creative Commons Attribution 4.0 International License, by Springer-Nature 2020.

arrangements. It is, however, still challenging to eliminate the electrode-level charge heterogeneity, which is partially due to the varying electron and ion accessibility at different locations in the electrodes. Reducing the electrode thickness can potentially suppress or eliminate the concentration gradient in the thickness direction. However, the lateral heterogeneity could persist even in the well-ordered thin electrode due to varying stack pressure. Furthermore, a recent study suggested that the intrinsic thermodynamic properties of electrode materials, such as the sensitivity of equilibrium potential to the state-of-charge (SOC), also impact the uniformity of reactions.³⁷

There are unavoidable limitations in some complicated experiments, setting a practical limit on how many particles one could study with a reasonable amount of effort. For example, the *in situ* and *operando* measurements of battery particles' responses to an externally applied reaction driving force (e.g., charging, thermal conditions) are often carried out on a small number of particles. It is also not possible to scan many particles using the 3D X-ray spectro-tomography method, which is a rather time-consuming measurement. In these characterizations for single particles or even local nanodomains, special attention is also warranted for improving the statistical representativeness. Multiple studies have shown that SOC distribution is heterogeneous not only in polycrystal-

line layered oxide particles (Figure 3) but also in single-crystal layered and spinel oxides. Xu et al. reported that the SOC distribution in polycrystalline NMC particles is guided by the crystallographic orientation of the primary grains. 19 The authors also performed a voxel-to-voxel analysis for about 20 million voxels to demonstrate the wide SOC distribution in individual secondary particles (Figure 3). The local SOC heterogeneity influences the chemomechanical stability. Therefore, the characterization techniques with high spatial resolution would need to screen many local nanodomains in the particle to obtain statistical representativeness. In a recent study, Jiang et al. 40 applied a soft X-ray nanoprobe technique to reveal the highly heterogeneous SOC distribution at the particle surface, consistent with the SOC tomography results reported by Xu et al.¹⁹ (Figure 3a). Such a complex system truly imposes remarkable challenges for characterization studies using techniques at a small length scale.

The materials electrochemistry in batteries is perhaps one of the most challenging systems of complex spatiotemporal heterogeneity. It has remained and will continue to be a challenge to bring together materials characterization at all relevant length scales. There is still a considerable gap between the current state-of-the-art and our ultimate goal of fully understanding the chemomechanical complexity in battery materials. Furthermore, the availability of experimental tools varies greatly across different research groups and countries. Nevertheless, we believe that improving data representativeness is critical and should be carefully addressed by researchers in the field.

In summary, we have noticed that current characterization literature has not considered multiscale heterogeneity enough. Multiscale chemomechanical heterogeneity is one of the underlying reasons for the underuse of the electrode capacity, causing locally overcharged and undercharged regions. If we can eliminate the charge heterogeneity, we can potentially improve the energy density and cycle life of the "old" commercialized battery materials. Through this Viewpoint, we hope to bring attention to the fact that biased conclusions can be made if no systematic, careful characterization is conducted. We recommend some strategies to improve the interpretation of mechanical properties and their relationship with battery performance:

- (1) Perform particle fracture characterization at different cycle numbers and different SOCs to understand how particle fracturing initiates and propagates.
- (2) Perform *in situ* measurements in a practically relevant sample environment (e.g., pouch cell).
- (3) Integrate the chemomechanical measurements with electroanalytical tools, such as electrochemical impedance spectroscopy.
- (4) Study as many particles and local domains as possible when using high spatial resolution tools.
- (5) *In situ* characterization is not consistently more elite than *ex situ* experiments, so combining *in situ* and *ex situ* measurements at different time and length scales can deliver a more complete picture.
- (6) 3D tomographic reconstruction with bulk microstructure sensitivity can provide more information than topographic imaging.
- (7) Perform experimental and modeling studies as independently as possible, so that no finite tuning of

- modeling parameters is performed to artificially improve the consistency.
- (8) Combine mechanical characterization with chemical analysis to understand the interplay between mechanics and chemistry.

Materials characterization has undergone a rapid development period in the past decade because of the need for better tools in battery research. With electron microscopy becoming more statistically representative and synchrotron X-ray techniques achieving higher spatial resolution while maintaining a large field of view, we believe that more will be uncovered regarding chemomechanical heterogeneity. Furthermore, the implementation of data analysis methods such as machinelearning approaches will shed light on a comprehensive understanding of the complex behavior of batteries. Riding on the learning curve, we call for an effort to tackle the frontier challenges in battery science with advanced and statistically significant materials characterization techniques. While our Viewpoint focuses on Li-ion cathodes, the opinions expressed here can be applied to investigate many more electrode materials, such as anodes with large volume changes.

Feng Lin © orcid.org/0000-0002-3729-3148 Kejie Zhao © orcid.org/0000-0001-5030-7412 Yijin Liu ® orcid.org/0000-0002-8417-2488

ASSOCIATED CONTENT

Supporting Information

The Supporting Information is available free of charge at https://pubs.acs.org/doi/10.1021/acsenergylett.1c02135.

Discussion of electron microscopy and X-ray imaging techniques and their advantages and disadvantages (PDF)

AUTHOR INFORMATION

Complete contact information is available at: https://pubs.acs.org/10.1021/acsenergylett.1c02135

Notes

The authors declare no competing financial interest. Views expressed in this Viewpoint are those of the authors and not necessarily the views of the ACS.

ACKNOWLEDGMENTS

The work at Virginia Tech is supported by the National Science Foundation under Grant No. DMR-1832613. The work at Purdue University is supported by the National Science Foundation under Grant No. DMR-1832707. Use of the Stanford Synchrotron Radiation Lightsource, SLAC National Accelerator Laboratory, is supported by the U.S. Department of Energy, Office of Science, Office of Basic Energy Sciences, under Contract No. DE-AC02-76SF00515. The hard X-ray phase contrast tomography was conducted at the Nano-Imaging beamline ID16A-NI at the ESRF, Grenoble, France. We would like to acknowledge Y. Yang, F. Monaco, and P. Cloetens for their collaboration in the tomographic experiments in our recent studies. Students and postdocs in our research groups are sincerely acknowledged for their continuing efforts in understanding, controlling, and improving the chemomechanical properties of battery materials.

REFERENCES

- (1) Koerver, R.; Zhang, W.; de Biasi, L.; Schweidler, S.; Kondrakov, A. O.; Kolling, S.; Brezesinski, T.; Hartmann, P.; Zeier, W. G.; Janek, J. Chemo-mechanical expansion of lithium electrode materials on the route to mechanically optimized all-solid-state batteries. *Energy Environ. Sci.* **2018**, *11* (8), 2142—2158.
- (2) Li, Y.; Cheng, X.; Zhang, Y.; Zhao, K. Recent advance in understanding the electro-chemo-mechanical behavior of lithium-ion batteries by electron microscopy. *Mater. Today Nano* **2019**, *7*, 100040.
- (3) Xu, Z.; Rahman, M. M.; Mu, L.; Liu, Y.; Lin, F. Chemomechanical behaviors of layered cathode materials in alkali metal ion batteries. *J. Mater. Chem. A* **2018**, *6* (44), 21859–21884.
- (4) Yan, P.; Zheng, J.; Gu, M.; Xiao, J.; Zhang, J.-G.; Wang, C.-M. Intragranular cracking as a critical barrier for high-voltage usage of layer-structured cathode for lithium-ion batteries. *Nat. Commun.* **2017**, 8 (1), 14101.
- (5) Xia, S.; Mu, L.; Xu, Z.; Wang, J.; Wei, C.; Liu, L.; Pianetta, P.; Zhao, K.; Yu, X.; Lin, F.; Liu, Y. Chemomechanical interplay of layered cathode materials undergoing fast charging in lithium batteries. *Nano Energy* **2018**, 53, 753–762.
- (6) Park, N.-Y.; Ryu, H.-H.; Park, G.-T.; Noh, T.-C.; Sun, Y.-K. Optimized Ni-Rich NCMA Cathode for Electric Vehicle Batteries. *Adv. Energy Mater.* **2021**, *11*, 2003767.
- (7) Park, G.-T.; Park, N.-Y.; Noh, T.-C.; Namkoong, B.; Ryu, H.-H.; Shin, J.-Y.; Beierling, T.; Yoon, C. S.; Sun, Y.-K. High-performance Ni-rich Li[Ni_{0.9-x}Co_{0.1}Al_x]O₂ cathodes via multi-stage microstructural tailoring from hydroxide precursor to the lithiated oxide. *Energy Environ. Sci.* **2021**, *14*, 5084–5095.
- (8) Lewis, J. A.; Cortes, F. J. Q.; Liu, Y.; Miers, J. C.; Verma, A.; Vishnugopi, B. S.; Tippens, J.; Prakash, D.; Marchese, T. S.; Han, S. Y.; Lee, C.; Shetty, P. P.; Lee, H.-W.; Shevchenko, P.; De Carlo, F.; Saldana, C.; Mukherjee, P. P.; McDowell, M. T. Linking void and interphase evolution to electrochemistry in solid-state batteries using operando X-ray tomography. *Nat. Mater.* **2021**, *20* (4), 503–510.
- (9) Lewis, J. A.; Tippens, J.; Cortes, F. J. Q.; McDowell, M. T. Chemo-Mechanical Challenges in Solid-State Batteries. *Trends Chem.* **2019**, *1* (9), 845–857.
- (10) Yang, Z.; Mu, L.; Hou, D.; Rahman, M. M.; Xu, Z.; Liu, J.; Nordlund, D.; Sun, C.-J.; Xiao, X.; Lin, F. Probing Dopant Redistribution, Phase Propagation, and Local Chemical Changes in the Synthesis of Layered Oxide Battery Cathodes. *Adv. Energy Mater.* **2021**, *11* (1), 2002719.
- (11) Yang, Z.; Lin, F. Heterogeneous, Defect-Rich Battery Particles and Electrodes: Why Do They Matter, and How Can One Leverage Them? *J. Phys. Chem. C* **2021**, *125* (18), 9618–9629.
- (12) Xu, Z.; Hou, D.; Kautz, D. J.; Liu, W.; Xu, R.; Xiao, X.; Lin, F. Charging Reactions Promoted by Geometrically Necessary Dislocations in Battery Materials Revealed by In Situ Single-Particle Synchrotron Measurements. *Adv. Mater.* **2020**, *32* (37), 2003417.
- (13) Mu, L.; Lin, R.; Xu, R.; Han, L.; Xia, S.; Sokaras, D.; Steiner, J. D.; Weng, T.-C.; Nordlund, D.; Doeff, M. M.; Liu, Y.; Zhao, K.; Xin, H. L.; Lin, F. Oxygen Release Induced Chemomechanical Breakdown of Layered Cathode Materials. *Nano Lett.* **2018**, *18* (5), 3241–3249.
- (14) Bi, Y.; Tao, J.; Wu, Y.; Li, L.; Xu, Y.; Hu, E.; Wu, B.; Hu, J.; Wang, C.; Zhang, J.-G.; Qi, Y.; Xiao, J. Reversible planar gliding and microcracking in a single-crystalline Ni-rich cathode. *Science* **2020**, 370 (6522), 1313–1317.
- (15) Rahman, M. M.; Lin, F. Oxygen Redox Chemistry in Rechargeable Li-Ion and Na-Ion Batteries. *Matter* **2021**, 4 (2), 490–527.
- (16) Kuppan, S.; Xu, Y.; Liu, Y.; Chen, G. Phase transformation mechanism in lithium manganese nickel oxide revealed by single-crystal hard X-ray microscopy. *Nat. Commun.* **2017**, *8* (1), 14309.
- (17) Yang, Y.; Xu, R.; Zhang, K.; Lee, S.-J.; Mu, L.; Liu, P.; Waters, C. K.; Spence, S.; Xu, Z.; Wei, C.; Kautz, D. J.; Yuan, Q.; Dong, Y.; Yu, Y.-S.; Xiao, X.; Lee, H.-K.; Pianetta, P.; Cloetens, P.; Lee, J.-S.; Zhao, K.; Lin, F.; Liu, Y. Quantification of Heterogeneous Degradation in Li-Ion Batteries. *Adv. Energy Mater.* **2019**, 9 (25), 1900674.

- (18) Gent, W. E.; Li, Y.; Ahn, S.; Lim, J.; Liu, Y.; Wise, A. M.; Gopal, C. B.; Mueller, D. N.; Davis, R.; Weker, J. N.; Park, J.-H.; Doo, S.-K.; Chueh, W. C. Persistent State-of-Charge Heterogeneity in Relaxed, Partially Charged $\text{Li}_{1-x}\text{Ni}_{1/3}\text{Co}_{1/3}\text{Mn}_{1/3}\text{O}_2$ Secondary Particles. *Adv. Mater.* **2016**, 28 (31), 6631–6638.
- (19) Xu, Z.; Jiang, Z.; Kuai, C.; Xu, R.; Qin, C.; Zhang, Y.; Rahman, M. M.; Wei, C.; Nordlund, D.; Sun, C.-J.; Xiao, X.; Du, X.-W.; Zhao, K.; Yan, P.; Liu, Y.; Lin, F. Charge distribution guided by grain crystallographic orientations in polycrystalline battery materials. *Nat. Commun.* **2020**, *11* (1), 83.
- (20) Mu, L.; Yuan, Q.; Tian, C.; Wei, C.; Zhang, K.; Liu, J.; Pianetta, P.; Doeff, M. M.; Liu, Y.; Lin, F. Propagation topography of redox phase transformations in heterogeneous layered oxide cathode materials. *Nat. Commun.* **2018**, *9* (1), 2810.
- (21) Lin, F.; Liu, Y.; Yu, X.; Cheng, L.; Singer, A.; Shpyrko, O. G.; Xin, H. L.; Tamura, N.; Tian, C.; Weng, T.-C.; Yang, X.-Q.; Meng, Y. S.; Nordlund, D.; Yang, W.; Doeff, M. M. Synchrotron X-ray Analytical Techniques for Studying Materials Electrochemistry in Rechargeable Batteries. *Chem. Rev.* **2017**, *117* (21), 13123–13186.
- (22) Qian, G.; Wang, J.; Li, H.; Ma, Z.-F.; Pianetta, P.; Li, L.; Yu, X.; Liu, Y. Structural and chemical evolution in layered oxide cathodes of lithium-ion batteries revealed by synchrotron techniques. *Nat. Sci. Rev.* **2021**. DOI: 10.1093/nsr/nwab146.
- (23) Wang, C.; Han, L.; Zhang, R.; Cheng, H.; Mu, L.; Kisslinger, K.; Zou, P.; Ren, Y.; Cao, P.; Lin, F.; Xin, H. L. Resolving atomic-scale phase transformation and oxygen loss mechanism in ultrahigh-nickel layered cathodes for cobalt-free lithium-ion batteries. *Matter* **2021**, *4* (6), 2013–2026.
- (24) Lu, X.; Bertei, A.; Finegan, D. P.; Tan, C.; Daemi, S. R.; Weaving, J. S.; O'Regan, K. B.; Heenan, T. M. M.; Hinds, G.; Kendrick, E.; Brett, D. J. L.; Shearing, P. R. 3D microstructure design of lithium-ion battery electrodes assisted by X-ray nano-computed tomography and modelling. *Nat. Commun.* **2020**, *11* (1), 2079.
- (25) Xu, R.; Yang, Y.; Yin, F.; Liu, P.; Cloetens, P.; Liu, Y.; Lin, F.; Zhao, K. Heterogeneous damage in Li-ion batteries: Experimental analysis and theoretical modeling. *J. Mech. Phys. Solids* **2019**, *129*, 160–183.
- (26) Qian, G.; Monaco, F.; Meng, D.; Lee, S.-J.; Zan, G.; Li, J.; Karpov, D.; Gul, S.; Vine, D.; Stripe, B.; Zhang, J.; Lee, J.-S.; Ma, Z.-F.; Yun, W.; Pianetta, P.; Yu, X.; Li, L.; Cloeten, P.; Liu, Y. The role of structural defects in commercial lithium-ion batteries. *Cell Rep. Phys. Sci.* **2021**, *2*, 100554.
- (27) Zan, G.; Zhang, J.; Monaco, F.; Gul, S.; Qian, G.; Li, J.; Vine, D. J.; Cloetens, P.; Yun, W.; Pianetta, P.; Liu, Y. Understanding multiscale battery degradation with a macro-to-nano zoom through its hierarchy. *J. Mater. Chem. A* **2021**, *9* (35), 19886–19893.
- (28) Lin, F.; Markus, I. M.; Nordlund, D.; Weng, T.-C.; Asta, M. D.; Xin, H. L.; Doeff, M. M. Surface reconstruction and chemical evolution of stoichiometric layered cathode materials for lithium-ion batteries. *Nat. Commun.* **2014**, *5* (1), 3529.
- (29) Liu, Y.; Harlow, J.; Dahn, J. Microstructural Observations of "Single Crystal" Positive Electrode Materials Before and After Long Term Cycling by Cross-section Scanning Electron Microscopy. *J. Electrochem. Soc.* **2020**, *167* (2), 020512.
- (30) Miller, D. J.; Proff, C.; Wen, J. G.; Abraham, D. P.; Bareño, J. Observation of Microstructural Evolution in Li Battery Cathode Oxide Particles by In Situ Electron Microscopy. *Adv. Energy Mater.* **2013**, 3 (8), 1098–1103.
- (31) Sim, R.; Lee, S.; Li, W.; Manthiram, A. Influence of Calendering on the Electrochemical Performance of $LiNi_{0.9}Mn_{0.05}Al_{0.05}O_2$ Cathodes in Lithium-Ion Cells. ACS Appl. Mater. Interfaces 2021, 13 (36), 42898–42908.
- (32) Harlow, J. E.; Ma, X.; Li, J.; Logan, E.; Liu, Y.; Zhang, N.; Ma, L.; Glazier, S. L.; Cormier, M. M. E.; Genovese, M.; Buteau, S.; Cameron, A.; Stark, J. E.; Dahn, J. R. A Wide Range of Testing Results on an Excellent Lithium-Ion Cell Chemistry to be used as Benchmarks for New Battery Technologies. *J. Electrochem. Soc.* 2019, 166 (13), A3031—A3044.

- (33) Huang, X.; Yang, J.; Mao, S.; Chang, J.; Hallac, P. B.; Fell, C. R.; Metz, B.; Jiang, J.; Hurley, P. T.; Chen, J. Controllable Synthesis of Hollow Si Anode for Long-Cycle-Life Lithium-Ion Batteries. *Adv. Mater.* **2014**, *26* (25), 4326–4332.
- (34) Sun, H. H.; Ryu, H.-H.; Kim, U.-H.; Weeks, J. A.; Heller, A.; Sun, Y.-K.; Mullins, C. B. Beyond Doping and Coating: Prospective Strategies for Stable High-Capacity Layered Ni-Rich Cathodes. ACS Energy Lett. 2020, 5, 1136–1146.
- (35) Li, L.; Erb, R. M.; Wang, J.; Wang, J.; Chiang, Y.-M. Fabrication of Low-Tortuosity Ultrahigh-Area-Capacity Battery Electrodes through Magnetic Alignment of Emulsion-Based Slurries. *Adv. Energy Mater.* **2019**, 9 (2), 1802472.
- (36) Li, J.; Leu, M. C.; Panat, R.; Park, J. A hybrid three-dimensionally structured electrode for lithium-ion batteries via 3D printing. *Mater. Des.* **2017**, *119*, 417–424.
- (37) Wang, F.; Tang, M. Thermodynamic Origin of Reaction Non-Uniformity in Battery Porous Electrodes and Its Mitigation. *J. Electrochem. Soc.* **2020**, *167* (12), 120543.
- (38) Xu, Y.; Hu, E.; Zhang, K.; Wang, X.; Borzenets, V.; Sun, Z.; Pianetta, P.; Yu, X.; Liu, Y.; Yang, X.-Q.; Li, H. In situ Visualization of State-of-Charge Heterogeneity within a LiCoO₂ Particle that Evolves upon Cycling at Different Rates. *ACS Energy Lett.* **2017**, 2 (5), 1240–1245.
- (39) Li, S.; Lee, S.-J.; Wang, X.; Yang, W.; Huang, H.; Swetz, D. S.; Doriese, W. B.; O'Neil, G. C.; Ullom, J. N.; Titus, C. J.; Irwin, K. D.; Lee, H.-K.; Nordlund, D.; Pianetta, P.; Yu, C.; Qiu, J.; Yu, X.; Yang, X.-Q.; Hu, E.; Lee, J.-S.; Liu, Y. Surface-to-Bulk Redox Coupling through Thermally Driven Li Redistribution in Li- and Mn-Rich Layered Cathode Materials. *J. Am. Chem. Soc.* **2019**, *141* (30), 12079—12086.
- (40) Jiang, Z.-S.; Li, S.-F.; Xu, Z.-R.; Nordlund, D.; Ohldag, H.; Pianetta, P.; Lee, J.-S.; Lin, F.; Liu, Y.-J. Revealing the inhomogeneous surface chemistry on the spherical layered oxide polycrystalline cathode particles. *Chin. Phys. B* **2020**, *29*, 026103.