

# Harnessing High Temporal Resolutions to Explore Fluxional Behavior on CeO<sub>2</sub> Nanoparticles under Reducing Conditions

R. Manzorro<sup>1</sup>, Y. Xu<sup>2</sup>, E. L. Lawrence<sup>1</sup>, D. Matteson<sup>2</sup>, P. A. Crozier<sup>1</sup>.

1. School for the Engineering of Matter, Transport, and Energy, Arizona State University, Tempe, Arizona


2. Department of Statistics and Data Science, Cornell, Ithaca, NY.

\* Corresponding author: peter.crozier@asu.edu

State-of-the-art, commercially available, direct electron detectors can acquire TEM series at up to 1000 frames per second (fps), capturing 1 ms snapshots of a materials system undergoing dynamic structural re-arrangement. In materials science in general, and catalysis in particular, this time regime may provide information on reaction paths, mechanisms or intermediate and metastable states of the evolving system. For example, fast structural re-arrangements at the atomic level under reaction conditions, known as fluxional behavior, are of increasing interest in catalysis [1]. Unfortunately, characterizing these dynamic events in the presence of gases and external stimuli without sacrificing either temporal or spatial resolutions is still a major challenge due to signal-to-noise (SNR) limitations.

To mitigate the SNR limitation, we have employed a high dose electron beam to drive chemical change in CeO<sub>2</sub> nanoparticles. Time-resolved *in situ* TEM images show the fluxional behavior of nanoparticles in strong reducing condition during illumination with a fluence rate of 120,000 e<sup>-</sup>Å<sup>-2</sup>s<sup>-1</sup> [2]. This electron fluence has been previously reported to induce surface CeO<sub>2</sub> reconfigurations at room temperature [3]. The 8913 frames time-series has been acquired in a Gatan K2 IS direct electron detector at 400 frames per second (2.5 ms each, 22.8 s in total), to track the evolution of CeO<sub>2</sub> fluxionality. New methodologies have been developed to deal first with large volume of data (almost 9,000 frames) and track atomic column position and intensity in very noisy conditions [4, 5].

A summed image (22.28 s) showing the average structure of the nanoparticle under consideration is shown in Figure 1a. At its top surface, two faint atomic columns (pointed with red arrows) are vaguely visible. The weak intensity suggests that the contribution of these two columns to the average image is very low, indicating a low frequency of occupancy throughout the entire series. Improving the time resolution to 50 ms by binning a smaller number of frames (20 frames) reveals the presence of very dynamic surface atomic columns, leading to structural re-arrangements of the nanofacet (Figure 1b, green arrows). The atomic configuration at these locations is changing from frame to frame, indicating that the lifetime of the structures is very low at this time scale (50 ms). Finally, temporal resolution has been improved to 2.5 ms per frame, as shown in Figure 1c. In addition to the surface reconfigurations happening on the 2.5 ms time frame, subsurface transformations are also observed with the appearance of local streaking columns in the planes shown in the blue boxes (round shape on the left, blurred and streaked on the right). This image streaking may be related to presence of shearing planes triggered by the electron beam removal of oxygen. Further analysis will be carried out to correlate the cationic migration observed at the top surface, where creation and annihilation of oxygen vacancies are required to allow cationic mobility, with the existence of local shear planes due to the lack of oxygen.

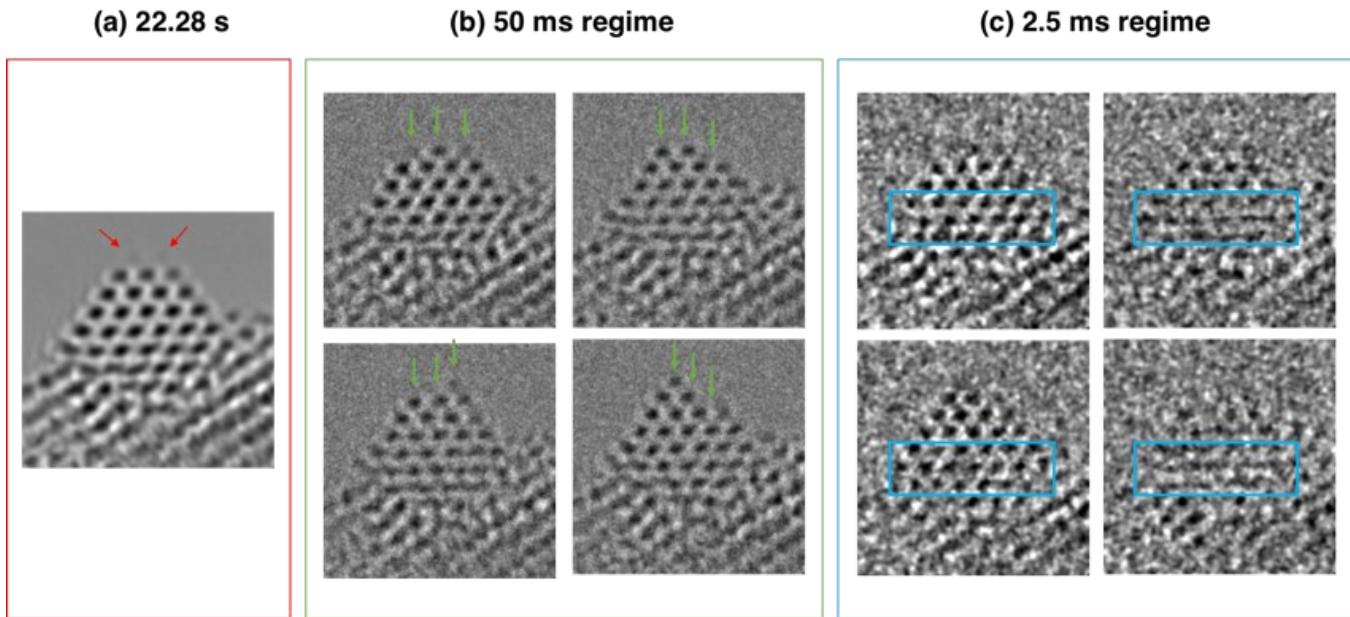

**Figure 1.** Subsets of the in situ TEM data illustrating the CeO<sub>2</sub> nanoparticle in a (110) orientation at different time resolutions. (a) Summed image of the 8,913 frames, leading to a 22.28 s image. (b) 20-frame average images, corresponding to a time resolution of 50 ms. (c) Single frames of the time series, acquired at 2.5 ms.

#### REFERENCES:

- [1] Vincent, J. L and Crozier, P. *Nat. Comm* **12** (2021) p. 5789. doi: 10.1038/s41467-021-26047-8
- [2] Lawrence, E. L. et al. *Micros. Microanal* **26** (2019) p. 86-94. doi: 10.1017/S1431927619015228
- [3] Bugnet, M. et al. *Nano Lett.* **17** (2017) p. 7652-7658. doi: 10.1021/acs.nanolett.7b03680
- [4] Manzorro, R. et al. *Micros. Microanal.* **27** (2021) p. 2224-2225. doi: 10.1017/S1431927621008011
- [5] Manzorro, R. et al. *submitted* (2021)
- [6] We gratefully acknowledge support of NSF OAC Award 1940263 supported RM and PAC. NSF OAC Award 1940124 and NSF CCF Award 1934985 supported DM and YC., and the facilities at ASU's John M. Cowley Center for High Resolution Electron Microscopy.

The authors gratefully acknowledge financial support from the National Science Foundation (NSF). NSF OAC Award 1940263 supported RM and PAC. NSF OAC Award 1940124 and NSF CCF Award 1934985 supported DM and YC. The authors acknowledge the John M. Cowley Center for High Resolution Electron Microscopy at Arizona State University.