

Ethylenediamine Addition Improves Performance and Suppresses Phase Instabilities in Mixed-Halide Perovskites

Margherita Taddei, Joel A. Smith, Benjamin M. Gallant, Suer Zhou, Robert J. E. Westbrook, Yangwei Shi, Jian Wang, James N. Drysdale, Declan P. McCarthy, Stephen Barlow, Seth R. Marder, Henry J. Snaith, and David S. Ginger*



Cite This: *ACS Energy Lett.* 2022, 7, 4265–4273



Read Online

ACCESS |



Metrics & More




Article Recommendations




Supporting Information

ABSTRACT: We show that adding ethylenediamine (EDA) to perovskite precursor solutions improves the photovoltaic device performance and material stability of high-bromide-content, methylammonium-free, formamidinium cesium lead halide perovskites $\text{FA}_{1-x}\text{Cs}_x\text{Pb}(\text{I}_{1-y}\text{Br}_y)_3$, which are currently of interest for perovskite-on-Si tandem solar cells. Using spectroscopy and hyperspectral microscopy, we show that the additive improves film homogeneity and suppresses the phase instability that is ubiquitous in high-Br perovskite formulations, producing films that remain stable for over 100 days in ambient conditions. With the addition of 1 mol % EDA, we demonstrate 1.69 eV-gap perovskite single-junction p-i-n devices with a V_{OC} of 1.22 V and a champion maximum-power-point-tracked power conversion efficiency of 18.8%, comparable to the best reported methylammonium-free perovskites. Using nuclear magnetic resonance (NMR) spectroscopy and X-ray diffraction techniques, we show that EDA reacts with FA^+ in solution, rapidly and quantitatively forming imidazolinium cations. It is the presence of imidazolinium during crystallization which drives the improved perovskite thin-film properties.


PL heterogeneity



EDA addition



PL homogeneity



Stability > 100 days in air
 V_{OC} 87% of radiative limit

Metal halide perovskites (MHPs) combine excellent semiconductor properties with the potential for scalable, low-cost manufacturing. As a result, these materials have attracted attention in optoelectronic applications ranging from photovoltaics,¹ light-emitting diodes,² and detectors³ to elements of nonlinear optics and sources of quantum light.⁴ MHPs have the generic formula ABX_3 , where A (= Cs^+ , methylammonium or MA^+ , formamidinium or FA^+) and B (= Pb^{2+} , Sn^{2+}) are cations and X (= I^- , Br^- , Cl^-) is an anion, and offer broad bandgap tunability from <1.25 eV in, e.g., $(\text{FASnI}_3)_{0.6}(\text{MAPbI}_3)_{0.4}$ to >2.25 eV in, e.g., CsPbBr_3 .^{5,6} In photovoltaics, there is particular interest in overcoming the single-junction, detailed-balance efficiency limit using multi-junction solar cells.^{7,8}

The ideal bandgap for the perovskite active layer in Si-perovskite tandem solar cells is roughly 1.7 eV.⁹ In order to achieve this bandgap for typical multication compositions, iodide is partially replaced with bromide at the halide (X^-) site, generally using over 23% Br^- .¹⁰ However, perovskites with high bromide/iodide ratios (>20%) usually undergo “halide segregation”, by which iodide-rich narrower bandgap regions are formed during illumination, compromising the performance and stability of the solar cell.^{11,12} In recent years, due to


thermal instabilities of methylammonium perovskites, compositions containing only formamidinium and cesium (FA^+/Cs^+) cations have been increasingly favored by the community.^{13,14} However, these FA^+/Cs^+ compositions suffer from phase instabilities over time: the desired cubic corner-sharing (α) “black” phases separate to pure CsPbI_3 and FAPbI_3 , which are 1D photoinactive, nonperovskite “yellow” phases in which the BX_6 octahedra are edge-sharing and face-sharing, respectively.¹⁵ Thus, it is necessary to find methods to limit both halide segregation and phase instability to achieve stable wide-gap compositions.

Diamines have previously been incorporated into metal halide perovskites as additives in the precursor solution.^{16–19} In particular, the addition of ethylenediamine (EDA) and ethylene diammonium iodide (EDAI_2) has been shown to lead

Received: September 3, 2022

Accepted: October 20, 2022

Published: November 2, 2022



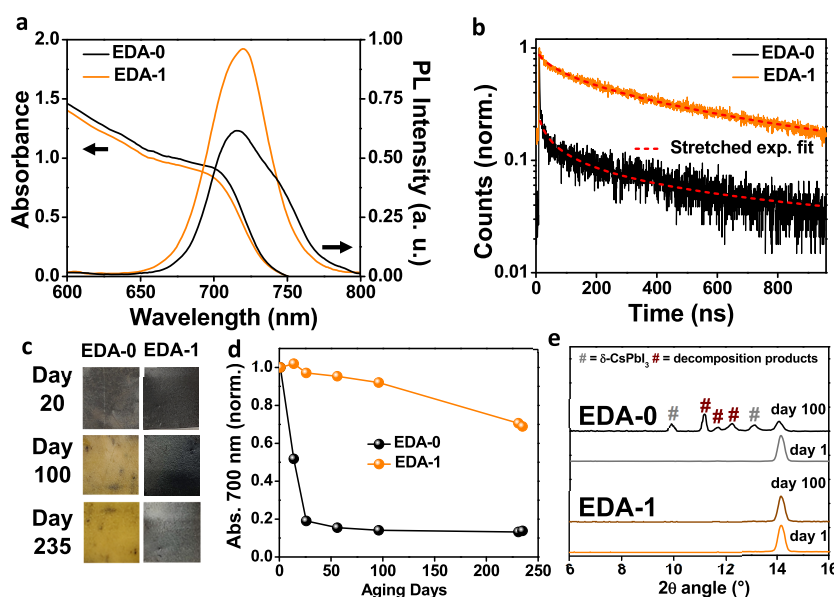


Figure 1. Material characterization and phase stability. (a) UV–vis spectra and normalized PL emission from films of $\text{FA}_{0.83}\text{Cs}_{0.17}\text{Pb}(\text{I}_{0.75}\text{Br}_{0.25})_3$ without EDA (EDA-0, black) and with 1% EDA (EDA-1, orange). The PL spectra are obtained using an integrating sphere coupled with a 532 nm laser. (b) Time resolved photoluminescence measurements using a 405 nm laser at 1 MHz pulse frequency. The fitting (dashed red line) was done using a stretched exponential decay. (c) Visual degradation of EDA-0 and EDA-1 exposed to air for 235 days. Samples were left unencapsulated in ambient air in the dark at an average room temperature of 19.5 °C and relative humidity of 31%. (d) Absorbance from UV–vis of EDA-0 (black) and EDA-1 (orange) at 700 nm during ambient aging. (e) XRD patterns in the $2\theta = 6\text{--}16^\circ$ region of the fresh EDA-0 (gray) and EDA-1 (orange) and after 100 days of ambient aging (EDA-0: black, EDA-1: brown).

to the formation of “hollow” materials in certain ABi_3 ($\text{A} = \text{MA}^+$, FA^+ ; $\text{B} = \text{Pb}^{2+}$, Sn^{2+}) perovskites, whereby diammonium dications are incorporated into the perovskite structure, along with B^{2+} and X^- vacancies, to enable steric accommodation of the EDA dications and balancing of the overall charge, respectively.^{20,21} In addition, the use of EDA via post-treatment of the surface has been reported to afford increased efficiency and stability in Pb–Sn perovskites.²² Likewise, dimethylammonium is another bulky cation, which is too large to incorporate into many halide perovskite compositions according to the Goldschmidt tolerance factor considerations but in some cases has been shown to increase both the bandgap, open-circuit voltage (V_{OC}) and overall performance of perovskite solar cells, despite negatively impacting the compositional heterogeneity of those films.^{23–25} Motivated by these observations, we hypothesized that the addition of EDA might be beneficial for formulations close to the 1.7 eV bandgap ideal for silicon-perovskite tandems. We anticipated that the addition of EDA might allow us to access a more stable compositional space, thus allowing the use of lower bromide concentrations to achieve the 1.7 eV bandgap ideal for silicon-perovskite tandems.

Here, we demonstrate that incorporating EDA into a >1.68 eV bandgap $\text{FA}_{0.83}\text{Cs}_{0.17}\text{Pb}(\text{I}_{0.75}\text{Br}_{0.25})_3$ perovskite yields a significant enhancement in both chemical homogeneity and phase stability as well as an enhancement of solar cell device performance. We show p–i–n devices with a maximum-power-point-tracked power conversion efficiency (PCE) of 18.8% and open-circuit voltage (V_{OC}) of 1.22 V with 1 mol % EDA (EDA-1) addition, which is a record for this bandgap in an MA-free composition. We investigate the mechanism for these improvements using nuclear magnetic resonance (NMR) spectroscopy and X-ray diffraction (XRD) techniques and find that EDA reacts with FA^+ in solution under the conditions employed here.

First, we investigate the effects of adding EDA to the growth solution used to deposit films of the composition $\text{FA}_{0.83}\text{Cs}_{0.17}\text{Pb}(\text{I}_{0.75}\text{Br}_{0.25})_3$, which has a bandgap close to the ideal top cell for a Si-tandem ($E_{\text{g}} = 1.695$ eV, extracted from UV–vis of Figure 1a). Figure 1a shows that addition of 1 mol % EDA (EDA-1) as an additive in the precursor solution used to spin-coat the films causes a very slight blueshift in the absorption ($E_{\text{g}} = 1.702$ eV) compared to those of the same composition without EDA (EDA-0), along with an increase in the measured photoluminescence intensity. PL measurements in an integrating sphere at an intensity of 60 mW/cm² with a 532 nm laser indicate that the EDA-1 film has a photoluminescence quantum efficiency (PLQE) of 9.7% and the emission maximum (λ_{max}) is located at 717 nm, whereas the EDA-0 sample has a PLQE of 6.5%, with its maximum at 722 nm (Figure S1). Figure 1a also shows that the EDA-0 film has a broader PL peak, with a clear shoulder at 744 nm. We observe this shoulder growing rapidly in EDA-0 samples, even during a brief PL measurement ($\sim$ time scale here 0.1s), consistent with reports of the facile segregation into I-rich and Br-rich phases for such high-bromide-composition samples.^{26–28}

Figure 1b shows the PL lifetime decays of the EDA-0 and EDA-1 films taken using 405 nm excitation with a pulse energy/area of ~ 4 nJ cm^{−2} ($n_0 = 1.8 \times 10^{14}$ cm^{−3}). Under these conditions, the differences in PL dynamics between the reference and EDA-1 films are clear, with the EDA-1 film showing a significantly longer PL lifetime. We fit the PL decays using a stretched exponential function, as we have reported previously:^{29,30}

$$I(t) = A_1 e^{-\left(\frac{t}{\tau}\right)^\beta} \quad (1)$$

We use the stretched exponential to account phenomenologically for distributions of PL lifetimes that carriers excited at

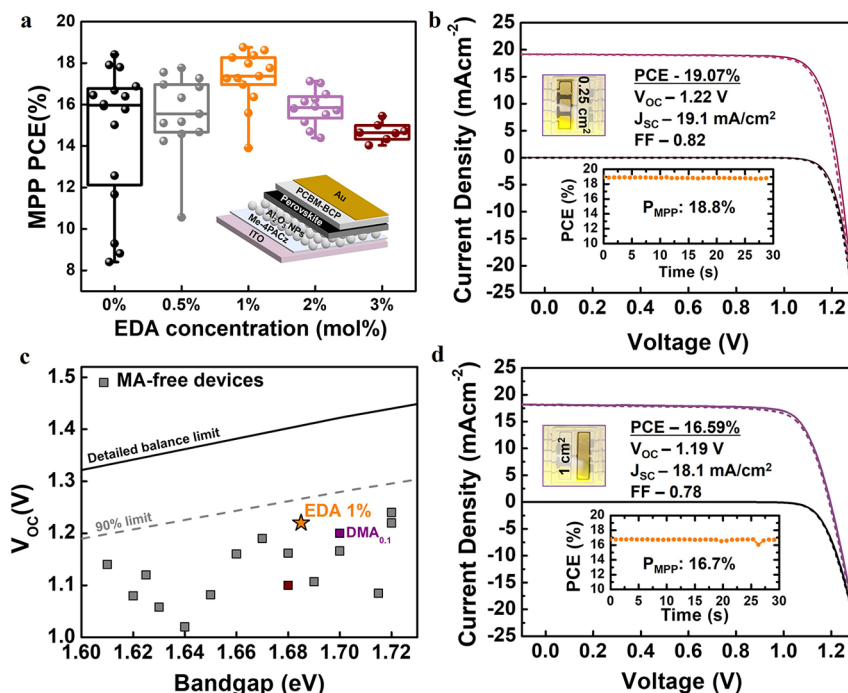


Figure 2. Photovoltaic device results. (a) Inset: Schematic of the perovskite solar cell device architecture we employ. Main: Efficiencies of solar cells made with 0–3 mol % EDA as an additive to the perovskite solution after 30 s of operation. (b) *JV* curves of the EDA-1 device under 1 sun simulated solar illumination, recorded in forward (from short to open circuit) and reverse (from open to short circuit) sweep directions. The inset tracks the PCE over 30 s of MPP-tracked device operation. Inset picture shows the device pixel area (0.25 cm²). (c) Open-circuit voltage (*V*_{OC}) results from the literature of wide-gap devices made with FA_{1−*x*}Cs_{*x*}Pb(I_{1−*x*}Br_{*x*})₃ compositions. The additives used in the best performing devices are noted next to the *V*_{OC} values. Purple data are from ref 23 using DMA⁺. Brown points are from ref 36 using the same perovskite composition as this work (FA_{0.83}Cs_{0.17}Pb(I_{0.75}Br_{0.25})₃). All references used in part (c) are given in Table S2. (d) *JV* curves of the EDA-1 large area champion device under 1 sun simulated solar illumination, recorded in forward (from short to open circuit) and reverse (from open to short circuit) sweep directions. The inset tracks the PCE over 30 s of MPP-tracked device operation. Inset picture shows the device pixel area (1 cm²).

different lateral and vertical positions in the film may experience due to sample heterogeneity. The stretched exponential fits for the reference and EDA-1 films give τ_c and beta values of $\tau_c = 0.6$ ns and $\beta = 0.17$ for the reference film and $\tau_c = 301.5$ ns and $\beta = 0.49$ for the EDA-1 films (see Table S1). The stretching exponent β is indicative of the width of the lifetime distribution in an ensemble sample, with a $\beta = 1$ recovering a perfectly homogeneous distribution of single-exponential emitters. Thus, the higher β value of the EDA-1 film (0.49) compared to that of the EDA-0 film (0.17) indicates a narrower distribution of emissive states, with the longer average lifetime τ_{stretch} calculated via

$$\tau_{\text{stretch}} = \frac{\tau_c}{\beta} \Gamma\left(\frac{1}{\beta}\right) \quad (2)$$

of 627 ns for the EDA-1 film compared to 411 ns for the EDA-0 film indicating a lower distribution of nonradiative recombination pathways in the EDA-1 film.

Next, we monitor the phase stability of unencapsulated films over time while storing them in ambient air, in the dark, at room temperature (ISOS D-1 conditions).³¹ Figure 1c shows the EDA-0 films rapidly (~days to weeks) revert to non-corner-sharing phases in ambient conditions, as previously reported,¹⁵ whereas the EDA-1 film is still predominantly in the desired photoactive black phase after 235 days. To quantify this stability, we use the UV–vis absorbance of the film at 700 nm as a proxy for the remaining pseudocubic perovskite. Figure 1d plots the resulting absorbance at 700 nm for each

film (full UV–vis spectra are shown in Figure S2). As is typical, the EDA-0 film shows a rapid, steep drop in optical density to less than 20% of the initial value after 25 days. In contrast, the EDA-1 maintains 96% of its initial absorbance after 100 days in an ambient environment. To characterize the phases formed during aging, we acquired XRD patterns of fresh films and after 100 days of aging in the same ambient conditions. In Figure 1e (full XRD patterns shown in Figure S3), the EDA-0 film shows the formation of several decomposition products including FAPbX₃ polytype phases, orthorhombic δ -CsPbX₃,³² and peaks consistent with a proposed CsPb₂I₄Br phase (Figure S4).³³ In contrast, EDA-1 shows no additional phases detectable by XRD after 100 days of aging. The stability was also tested under accelerated conditions with ambient light and air flow where we note that stability was further enhanced with 10 mol % EDA (EDA-10), shown in Figure S5.

Given the promising increases in stability, PLQE, and PL lifetime, we fabricated p-i-n solar cells using EDA as an additive, with the device architecture glass/ITO/Me-4PACz/np-Al₂O₃/perovskite/PCBM/BCP/Au, where Me-4PACz is a carbazole-based self-assembled monolayer (SAM) hole extraction layer ([4-(3,6-dimethyl-9H-carbazol-9-yl)butyl]-phosphonic acid), np-Al₂O₃ is a dilute nanoparticle alumina layer employed to improve the perovskite solution wetting, PCBM ([6,6]-phenyl-C61-butyric acid methyl ester) is the electron extraction layer, and BCP (bathocuproine) rectifies the fullerene/metal junction.³⁴ Employing perovskite precursor solutions with a range of EDA additions from 0–3 mol % had a

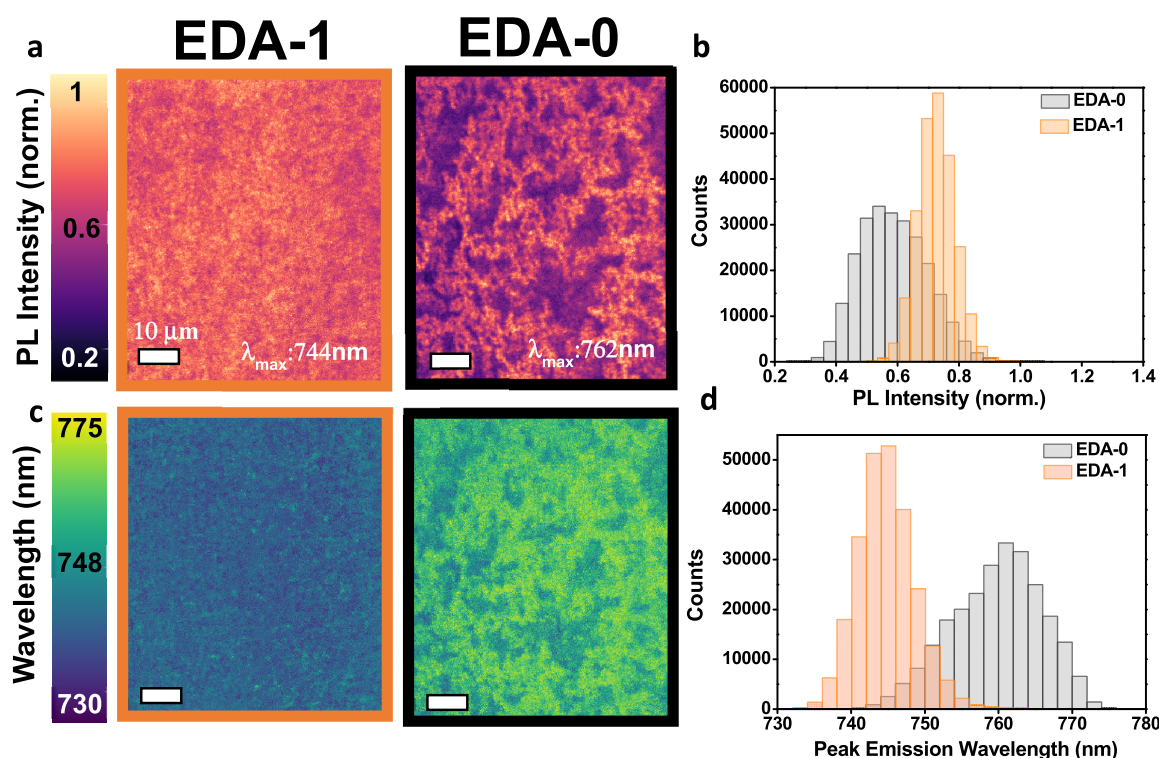


Figure 3. Halide heterogeneity on the microscale. (a) Hyperspectral PL intensity map of the EDA-0 (black box) and EDA-1 (orange box). PL images are shown at the maximum emission wavelength (λ_{max}) for each sample as stated on the figure (EDA-0 $\lambda_{\text{max}} = 762 \text{ nm}$, EDA-1 $\lambda_{\text{max}} = 744 \text{ nm}$). Excitation was achieved with a white lamp with short pass filter at 500 nm. The emission was recorded using a 500 nm dichroic and 550 nm long pass filter. (b) Histogram of the PL intensity distribution at the maximum emission wavelength for EDA-0 (gray) and EDA-1 (orange) samples. (c) Peak emission wavelength map of the EDA-0 and EDA-1 films. (d) Histogram of the distribution of peak emission wavelengths for the EDA-0 (gray) and EDA-1 (orange) samples.

marked effect on the device performance measured under standard conditions (full details given in the [Methods](#)). [Figure 2a](#) shows stabilized maximum power point (MPP) efficiencies of the resulting devices (0.25 cm^2 active area), with the MPP shown for more representative performance comparison.³⁵ The full current–voltage (*JV*) performance metrics—power conversion efficiency (PCE), short-circuit current density (J_{SC}), fill factor (FF), and open-circuit voltage (V_{OC})—are shown in [Figure S6](#). The V_{OC} increases steadily with EDA addition over the concentration series, which we propose could be due to a combination of passivation and/or blueshift effects with the additive. Both J_{SC} and FF reach a maximum at 1% EDA, with a particularly severe decline in J_{SC} above this optimum value probably related to the lower relative absorbance and blueshift of the band edge with additional EDA.

[Figure 2b](#) shows the *JV* results from the best EDA-1 device with a maximum PCE of 19.07%, V_{OC} of 1.22 V, J_{SC} of 19.1 mA/cm^2 , and FF of 82%, with little observable hysteresis. We verified the measured J_{SC} using external quantum efficiency (EQE) measurements, with the integrated current over the spectral range in perfect agreement with the *JV*-determined J_{SC} ([Figure S7](#)). The results for the EDA-1 device were compared to the literature on MA-free wide-gap compositions ([Table S2](#)).

Our champion 19.07% PCE for a 1.685 eV bandgap composition compares favorably to other reports ([Figure S8](#)), in particular the high V_{OC} of 1.22 V, shown in [Figure 2c](#). Additionally, in [Figure S9](#), we show the performance for larger 1 cm^2 devices fabricated in the same batches and on the same device substrates as the smaller area cells (0.25 cm^2). Notably,

EDA-1 devices show significantly higher average and champion efficiencies compared to without the additive. In [Figure 2d](#), we show the *JV* curve and stabilized MPP tracking of the champion EDA-1 large area device (16.7% MPP PCE). We attribute this improvement to an improvement in the spin-coated film morphology over larger areas, which is crucial for any precursor solution to be suitable for scale-up and leads us to investigate film morphology further.

To better understand the origins of the improved stability, PL, and device performance, we explored how the PL varied on the microscale using hyperspectral microscopy ([Figure 3a,c](#)). A hyperspectral microscope obtains a PL spectrum at every pixel with high spatial resolution (for setup details see methods section) and has been used to spatially resolve heterogeneity in perovskites^{37–39} and other semiconductors. [Figure 3b,d](#) plots summaries of the hyperspectral data cubes showing the wavelength-integrated total PL intensity as well as the peak emission wavelength at every point in the sample. These measurements show that the EDA-1 processed films are significantly more homogeneous in both PL intensity and PL peak wavelength than the EDA-0 films. The luminescent regions in EDA-0 are more red-shifted in accordance with them being more iodide-rich, narrower gap regions, into which charge carriers are funneled and recombine radiatively with high efficiency.^{11,40} Generally, these microscopic results provide insight into the area-averaged spectra shown in [Figure 1](#). Indeed, the histogram in [Figure 3b](#) shows the reference films exhibit a much wider distribution of local PL intensities, with many areas of the film being effectively dark. Similarly, the peak emission wavelength is also affected by the additive.

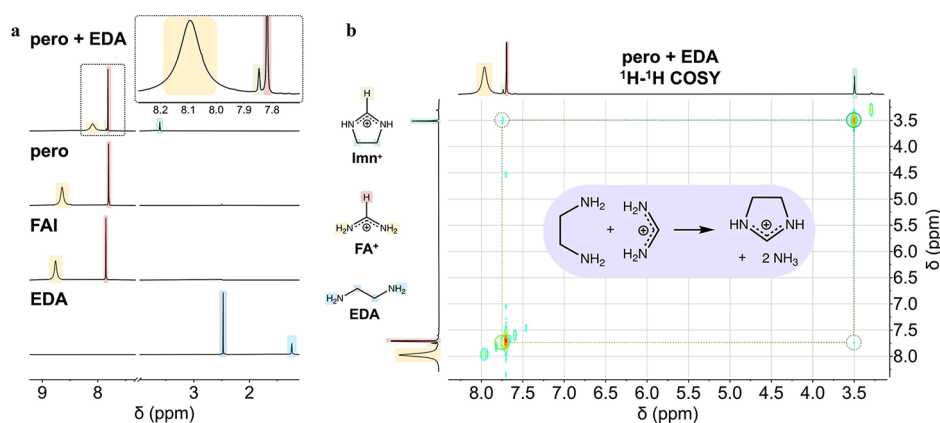


Figure 4. Chemical origins of EDA effects (a) ^1H solution NMR spectra of (bottom to top) ethylenediamine (EDA), formamidinium iodide (FAI), and $(\text{FA}_{0.83}\text{Cs}_{0.17})\text{Pb}(\text{I}_{0.75}\text{Br}_{0.25})_3$ without (pero) and with 10 mol % EDA added (pero + EDA). (b) ^1H – ^1H correlation spectroscopy (COSY) of $(\text{FA}_{0.83}\text{Cs}_{0.17})\text{Pb}(\text{I}_{0.75}\text{Br}_{0.25})_3$ with 10 mol % EDA added. Off-diagonal correlation indicates corresponding ^1H chemical environments are spin–spin coupled. All materials are dissolved in d_6 DMSO. The inset highlighted in purple shows the overall reaction of FA^+ with EDA to produce Imn^+ and ammonia.

Whereas the local emission peak wavelength varies between ~ 720 to 780 nm in the reference films, the EDA-1 films show a narrow clustering of the emission peaking around ~ 744 nm, consistent with the area-averaged data (Figure 3d). These data help explain the improved stability and device performance. The increased PLQE indicates a reduction in trap density in the EDA-1 films, facilitating larger quasi-Fermi-level splitting under illumination and therefore increased V_{OC} ,^{41–43} and additionally, the improved homogeneity could help improve V_{OC} of the EDA-1 films by reducing pinning to the low-bandgap regions of the film, which is a common problem in complex semiconductors.^{44,45} Moreover, it has been shown recently that compositional inhomogeneity of the perovskite phase is the primary cause of phase instability in $\text{FA}_{1-x}\text{Cs}_x\text{Pb}(\text{I}_{1-y}\text{Br}_y)_3$ perovskites.^{46–48} Figure S10 shows the formation of “wrinkled”^{49–52} films when using a higher precursor solution concentration (1.45 M). Even in this case, EDA-1 films show more homogeneous PL intensity and wavelength distributions compared to EDA-0. Figure S11 also shows 10 mol % addition of EDA (EDA-10) yields homogenized PL and emission wavelength distribution on the microscale. Several studies have shown that light and oxygen induce halide segregation in mixed-cation mixed-halide compositions.^{53,54} In Figure S12, we show with hyperspectral imaging that under constant illumination unencapsulated control films are more heterogeneous than films with EDA addition. To further investigate the compositional variation between the samples, we performed scanning electron microscopy energy-dispersive X-ray analysis (SEM EDS) at various points over the film surfaces for the EDA-0 and EDA-10 films. Figure S13 shows that the EDA-0 film has greater variation in atomic composition compared to the narrowly distributed EDA-10 film.

To better understand the effects of EDA addition on film formation, we investigated the crystallization of films by blade coating solutions and acquiring *in situ* grazing-incidence wide-angle X-ray scattering (GIWAXS) measurements (described in the Methods, scheme shown in Figure S14). For all samples (0, 1, and 10% EDA), we identify that there exists an intermediate phase, which is a 2H polytype.⁵⁵ In the EDA-0 sample, this phase subsequently converts fully into a pseudocubic (3C) perovskite phase upon annealing (Figure S15a). However, with EDA-10, we find that in addition to the corner-sharing (α)

perovskite phase, a different 2H polytype and a 4H polytype^{55,56} are also formed in the fully annealed films (Figure S15c). For the EDA-1 sample, we detect a weak signature of a new polytype (Figure S15f). These results indicate that the EDA additive is altering the growth and resultant film composition at the studied concentrations.

In the SI, we investigate and discuss the impact of higher EDA concentrations upon crystallization and phase behavior in thin films (SI Note 1, Figures S16–S19 and S21–S26). Significantly, we note that the XRD peaks from the 2H phase at a high EDA concentration (40 mol %) are a close match for a reported imidazolium lead iodide (ImPbI_3) 2H phase (Figure S20).^{57,58} We therefore investigated the possibility of larger cations forming in solution by conducting a range of NMR measurements. In Figure 4a, we show ^1H NMR spectra of our perovskite precursor materials with and without 10 mol % EDA and compare these to neat FAI and EDA, with all materials dissolved in d_6 -DMSO (full spectra in Figure S27). Unexpectedly, the addition of 10 mol % EDA does not lead to the appearance of the signals observed for neat EDA (δ 2.47, 1.23 ppm) but instead to the appearance of two new ^1H signals at 7.85 ppm (1H, t) and 3.62 ppm (4H, s). ^1H – ^1H correlation spectroscopy (COSY) reveals off-diagonal signals demonstrating spin–spin coupling between these two new signals, indicating that they correspond to ^1H environments in the same molecule (Figure 4b). In ^{13}C NMR (Figure S28), signals observed in spectra acquired from EDA, FAI, and perovskite solutions correspond to the expected ^{13}C environments. However, in the EDA-10 precursor solution, we again observe two unexpected ^{13}C signals and the absence of a signal corresponding to the carbon environment of neat EDA. Significantly, ^1H – ^{13}C heteronuclear single quantum correlation (HSQC) spectroscopy of the EDA-10 precursor solution (Figure S29) reveals that the proton giving rise to the unexpected signal at 3.62 ppm is bonded to the carbon corresponding to the signal observed at 48.6 ppm, suggesting the presence of a new alkyl carbon bonded to an electronegative atom. The proximity of the new ^1H and ^{13}C signals at 7.85 and 161.9 ppm, respectively, to those corresponding to the methine environment of FA^+ suggests that the new species formed in solution also contains an amidinium group. The ^1H signal at 3.62 ppm is shown to be both attached to an alkyl

carbon and spin–spin coupled to the new ^1H methine environment strongly implies the formation of a new species in solution by direct reaction between FA^+ and EDA. The 4:1 stoichiometry of alkyl:methine ^1H signals suggests a 1:1 reaction. As the four alkyl hydrogens of EDA remain equivalent in the new species, we deduce that the symmetry of both FA^+ and EDA is retained in the new species.

Given these findings, we propose that consecutive addition–elimination reactions occur in solution leading to the formation of a secondary amidinium cation contained within a five-membered ring, 2-imidazolinium (4,5-dihydroimidazolium, $\text{C}_3\text{H}_7\text{N}_2^+$, Imn^+), and the elimination of 2 equiv. of volatile ammonia (inset of Figure 4b). We account mechanistically for this reaction in Figure S30. Such amine–amidinium reactions have precedent in recent perovskite literature,^{59,60} and specifically, this reaction is noted in early synthesis protocols for imidazolines.⁶¹ To further support the proposed formation of Imn^+ , time-of-flight secondary ion mass spectrometry (ToF-SIMS) (Figure S31) data shows a high-intensity $\text{C}_3\text{H}_7\text{N}_2^+$ mass fragment consistent with the formation of a Imn^+ in the EDA-1 and EDA-20 films.

With this reaction, we can rationalize why, in our study, the EDA additive does not result in a hollow perovskite, as in previous works EDA was generally employed in acidic growth conditions and so is easily protonated. Under such conditions, or in solutions where EDA^{2+} is added directly, there is only a negligible quantity of ethylenediamine present at any time. As the diamine nucleophile is necessary to produce Imn^+ via reaction with FA^+ , such conditions would effectively prevent its formation. To support this hypothesis, we verified that we do not form any polytype phases when we add the diammonium salts EDAH_2I_2 or EDAH_2Br_2 (Figure S32) or when we only have MA^+ rather than FA^+ in solution (Figure S33). The lattice volume expands in such cases, indicating EDA/ EDA^+ inclusion.

While it is clear that EDA is converted to imidazolinium, typically before the film is even spin-coated, and that the resulting films are more homogeneous, the exact impact of the imidazolinium remains open for further investigation. We hypothesize that the imidazolinium, and the associated 2H polytype phases, could play a variety of roles including passivating exposed interfaces, helping nucleate or template the growth of the desired perovskite phase, or even serve as a reservoir of halide ions, sequestering them from the active perovskite phase.

In summary, we see that EDA has a beneficial effect on the stability of MA^+ -free mixed-cation mixed-halide perovskite compositions. We are able to achieve an outstanding V_{OC} and MPP-tracked PCE of 1.22 V and 18.8%, respectively, for MA^+ -free devices with a bandgap of ~ 1.7 eV (1.69 eV), which is highly suitable for perovskite-on-Si tandem devices. We observe that EDA reacts with FA^+ in solution to form imidazolinium, which impacts the thin-film crystallization pathway and correlates with significantly improved compositional homogeneity, thin-film ambient stability, and device performance. Importantly, this approach of using amine additives can be generalized to the production of other amidinium-derived compounds and may enable a range of species which are otherwise challenging to isolate. Similar approaches could be used to further engineer the surface chemistry and enhance the stability of halide perovskites.

■ ASSOCIATED CONTENT

SI Supporting Information

The Supporting Information is available free of charge at <https://pubs.acs.org/doi/10.1021/acsenenergylett.2c01998>.

Experimental methods, including thin-film synthesis, spectroscopic and microscopic characterization, device fabrication, and testing, further supporting discussion on GIWAXS and XRD data, additional references and figures (PDF)

■ AUTHOR INFORMATION

Corresponding Author

David S. Ginger – Department of Chemistry, University of Washington, Seattle, Washington 98195, United States; orcid.org/0000-0002-9759-5447; Email: dginger@uw.edu

Authors

Margherita Taddei – Department of Chemistry, University of Washington, Seattle, Washington 98195, United States; orcid.org/0000-0003-4122-8418

Joel A. Smith – Department of Physics, University of Oxford, Oxford OX1 3PU, U.K.; orcid.org/0000-0001-6889-4408

Benjamin M. Gallant – Department of Physics, University of Oxford, Oxford OX1 3PU, U.K.

Suer Zhou – Department of Physics, University of Oxford, Oxford OX1 3PU, U.K.

Robert J. E. Westbrook – Department of Chemistry, University of Washington, Seattle, Washington 98195, United States; Molecular Engineering & Sciences Institute, University of Washington, Seattle, Washington 98195, United States

Yangwei Shi – Department of Chemistry, University of Washington, Seattle, Washington 98195, United States; orcid.org/0000-0002-9014-7422

Jian Wang – Department of Chemistry, University of Washington, Seattle, Washington 98195, United States; orcid.org/0000-0002-4515-9782

James N. Drysdale – Department of Physics, University of Oxford, Oxford OX1 3PU, U.K.

Declan P. McCarthy – Renewable and Sustainable Energy Institute, University of Colorado Boulder, Boulder, Colorado 80303, United States

Stephen Barlow – Renewable and Sustainable Energy Institute, University of Colorado Boulder, Boulder, Colorado 80303, United States; orcid.org/0000-0001-9059-9974

Seth R. Marder – Renewable and Sustainable Energy Institute and Department of Chemical and Biological Engineering and Department of Chemistry, University of Colorado Boulder, Boulder, Colorado 80303, United States; orcid.org/0000-0001-6921-2536

Henry J. Snaith – Department of Physics, University of Oxford, Oxford OX1 3PU, U.K.; orcid.org/0000-0001-8511-790X

Complete contact information is available at: <https://pubs.acs.org/doi/10.1021/acsenenergylett.2c01998>

Notes

The authors declare the following competing financial interest(s): H.J.S. is a cofounder and CSO of Oxford PV Ltd.

ACKNOWLEDGMENTS

This paper is based on work supported primarily by the Office of Naval Research (Award # N00014-20-1-2587). ToF-SIMS and part of the XRD analysis were carried out at the Molecular Analysis Facility, a National Nanotechnology Coordinated Infrastructure site at the University of Washington which is supported in part by the National Science Foundation (NNCI-1542101), the Molecular Engineering & Sciences Institute, and the Clean Energy Institute. The SEM analysis was carried out in the UW Clean Energy Institute Research Training Testbed facility. TRPL and some PL measurements were performed using the shared user facilities of UW's Molecular Engineering Materials Center, an NSF MRSEC (DMR-1719797). M.T. thanks Dan Graham at the Molecular Analysis Facility at the University of Washington for his help with ToF-SIMS data collection and analysis and Hannah Contreras for experimental help. D.S.G. acknowledges salary and infrastructure support from the Washington Research Foundation, the Alvin L. and Verla R. Kwiram endowment, and the B. Seymour Rabinovitch Endowment. S.Z. acknowledges receiving funding from the Rank Prize Funds. We acknowledge Diamond Light Source for time on beamline I07 under proposal SI30612-1 for the GIWAXS measurements and thank Saqlain Choudhary and Dr. Hadeel Hussain for assistance and Dr. Daniel Toolan and Karl-Augustin Zaininger for use of the *in situ* blade coater during these experiments.

REFERENCES

- (1) Correa-Baena, J.-P.; Saliba, M.; Buonassisi, T.; Grätzel, M.; Abate, A.; Tress, W.; Hagfeldt, A. Promises and Challenges of Perovskite Solar Cells. *Science* **2017**, *358* (6364), 739–744.
- (2) Lin, K.; Xing, J.; Quan, L. N.; de Arquer, F. P. G.; Gong, X.; Lu, J.; Xie, L.; Zhao, W.; Zhang, D.; Yan, C.; Li, W.; Liu, X.; Lu, Y.; Kirman, J.; Sargent, E. H.; Xiong, Q.; Wei, Z. Perovskite Light-Emitting Diodes with External Quantum Efficiency Exceeding 20 per Cent. *Nature* **2018**, *562* (7726), 245–248.
- (3) Basiricò, L.; Ciavatti, A.; Fraboni, B. Solution-Grown Organic and Perovskite X-Ray Detectors: A New Paradigm for the Direct Detection of Ionizing Radiation. *Advanced Materials Technologies* **2021**, *6* (1), 2000475.
- (4) Muckel, F.; Guye, K. N.; Gallagher, S. M.; Liu, Y.; Ginger, D. S. Tuning Hybrid Exciton–Photon Fano Resonances in Two-Dimensional Organic–Inorganic Perovskite Thin Films. *Nano Lett.* **2021**, *21* (14), 6124–6131.
- (5) Li, C.; Song, Z.; Chen, C.; Xiao, C.; Subedi, B.; Harvey, S. P.; Shrestha, N.; Subedi, K. K.; Chen, L.; Liu, D.; Li, Y.; Kim, Y.-W.; Jiang, C.; Heben, M. J.; Zhao, D.; Ellingson, R. J.; Podraza, N. J.; Al-Jassim, M.; Yan, Y. Low-Bandgap Mixed Tin–Lead Iodide Perovskites with Reduced Methylammonium for Simultaneous Enhancement of Solar Cell Efficiency and Stability. *Nat. Energy* **2020**, *5* (10), 768–776.
- (6) Kulbak, M.; Cahen, D.; Hodes, G. How Important Is the Organic Part of Lead Halide Perovskite Photovoltaic Cells? Efficient CsPbBr₃ Cells. *J. Phys. Chem. Lett.* **2015**, *6* (13), 2452–2456.
- (7) McMeekin, D. P.; Sadoughi, G.; Rehman, W.; Eperon, G. E.; Saliba, M.; Horantner, M. T.; Haghighirad, A.; Sakai, N.; Korte, L.; Rech, B.; Johnston, M. B.; Herz, L. M.; Snaith, H. J. A Mixed-Cation Lead Mixed-Halide Perovskite Absorber for Tandem Solar Cells. *Science* **2016**, *351* (6269), 151–155.
- (8) Leijtens, T.; Bush, K. A.; Prasanna, R.; McGehee, M. D. Opportunities and Challenges for Tandem Solar Cells Using Metal Halide Perovskite Semiconductors. *Nat. Energy* **2018**, *3* (10), 828–838.
- (9) Eperon, G. E.; Hörantner, M. T.; Snaith, H. J. Metal Halide Perovskite Tandem and Multiple-Junction Photovoltaics. *Nat. Rev. Chem.* **2017**, *1* (12), 0095.
- (10) Lin, Y.-H.; Sakai, N.; Da, P.; Wu, J.; Sansom, H. C.; Ramadan, A. J.; Mahesh, S.; Liu, J.; Oliver, R. D. J.; Lim, J.; Aspartate, L.; Sharma, K.; Madhu, P. K.; Morales-Vilches, A. B.; Nayak, P. K.; Bai, S.; Gao, F.; Grovenor, C. R. M.; Johnston, M. B.; Labram, J. G.; Durrant, J. R.; Ball, J. M.; Wenger, B.; Stannowski, B.; Snaith, H. J. A Piperidinium Salt Stabilizes Efficient Metal-Halide Perovskite Solar Cells. *Science* **2020**, *369* (6499), 96–102.
- (11) Motti, S. G.; Patel, J. B.; Oliver, R. D. J.; Snaith, H. J.; Johnston, M. B.; Herz, L. M. Phase Segregation in Mixed-Halide Perovskites Affects Charge-Carrier Dynamics While Preserving Mobility. *Nat. Commun.* **2021**, *12* (1), 6955.
- (12) Wieghold, S.; Tresback, J.; Correa-Baena, J.-P.; Hartono, N. T. P.; Sun, S.; Liu, Z.; Layurova, M.; VanOrman, Z. A.; Bieber, A. S.; Thapa, J.; Lai, B.; Cai, Z.; Nienhaus, L.; Buonassisi, T. Halide Heterogeneity Affects Local Charge Carrier Dynamics in Mixed-Ion Lead Perovskite Thin Films. *Chem. Mater.* **2019**, *31* (10), 3712–3721.
- (13) Juarez-Perez, E. J.; Ono, L. K.; Maeda, M.; Jiang, Y.; Hawash, Z.; Qi, Y. Photodecomposition and Thermal Decomposition in Methylammonium Halide Lead Perovskites and Inferred Design Principles to Increase Photovoltaic Device Stability. *J. Mater. Chem. A* **2018**, *6* (20), 9604–9612.
- (14) Conings, B.; Drijkoningen, J.; Gauquelin, N.; Babayigit, A.; D'Haen, J.; D'Olieslaeger, L.; Ethirajan, A.; Verbeeck, J.; Manca, J.; Mosconi, E.; Angelis, F. D.; Boyen, H.-G. Intrinsic Thermal Instability of Methylammonium Lead Trihalide Perovskite. *Adv. Energy Mater.* **2015**, *5* (15), 1500477.
- (15) An, Y.; Hidalgo, J.; Perini, C. A. R.; Castro-Méndez, A.-F.; Vagott, J. N.; Bairley, K.; Wang, S.; Li, X.; Correa-Baena, J.-P. Structural Stability of Formamidinium- and Cesium-Based Halide Perovskites. *ACS Energy Lett.* **2021**, *6* (5), 1942–1969.
- (16) Kerner, R. A.; Schloemer, T. H.; Schulz, P.; Berry, J. J.; Schwartz, J.; Sellinger, A.; Rand, B. P. Amine Additive Reactions Induced by the Soft Lewis Acidity of Pb²⁺ in Halide Perovskites. Part II: Impacts of Amido Pb Impurities in Methylammonium Lead Triiodide Thin Films. *J. Mater. Chem. C* **2019**, *7* (18), 5244–5250.
- (17) Kerner, R. A.; Schloemer, T. H.; Schulz, P.; Berry, J. J.; Schwartz, J.; Sellinger, A.; Rand, B. P. Amine Additive Reactions Induced by the Soft Lewis Acidity of Pb²⁺ in Halide Perovskites. Part I: Evidence for Pb–Alkylamide Formation. *J. Mater. Chem. C* **2019**, *7* (18), 5251–5259.
- (18) Wu, W.-Q.; Yang, Z.; Rudd, P. N.; Shao, Y.; Dai, X.; Wei, H.; Zhao, J.; Fang, Y.; Wang, Q.; Liu, Y.; Deng, Y.; Xiao, X.; Feng, Y.; Huang, J. Bilateral Alkylamine for Suppressing Charge Recombination and Improving Stability in Blade-Coated Perovskite Solar Cells. *Science Advances* **2019**, *5* (3), eaav8925.
- (19) Xu, Y.; Xu, W.; Hu, Z.; Steele, J. A.; Wang, Y.; Zhang, R.; Zheng, G.; Li, X.; Wang, H.; Zhang, X.; Solano, E.; Roelofs, M. B. J.; Uvdal, K.; Qing, J.; Zhang, W.; Gao, F. Impact of Amine Additives on Perovskite Precursor Aging: A Case Study of Light-Emitting Diodes. *J. Phys. Chem. Lett.* **2021**, *12* (25), 5836–5843.
- (20) Ke, W.; Stoumpos, C. C.; Zhu, M.; Mao, L.; Spanopoulos, I.; Liu, J.; Kontsevoi, O. Y.; Chen, M.; Sarma, D.; Zhang, Y.; Wasielewski, M. R.; Kanatzidis, M. G. Enhanced Photovoltaic Performance and Stability with a New Type of Hollow 3D Perovskite {en}FASnI₃. *Sci. Adv.* **2017**, *3* (8), e1701293.
- (21) Li, C.; Guerrero, A.; Huettner, S.; Bisquert, J. Unravelling the Role of Vacancies in Lead Halide Perovskite through Electrical Switching of Photoluminescence. *Nat. Commun.* **2018**, *9* (1), 5113.
- (22) Hu, S.; Otsuka, K.; Murdey, R.; Nakamura, T.; Truong, M. A.; Yamada, T.; Handa, T.; Matsuda, K.; Nakano, K.; Sato, A.; Marumoto, K.; Tajima, K.; Kanemitsu, Y.; Wakamiya, A. Optimized Carrier Extraction at Interfaces for 23.6% Efficient Tin–Lead Perovskite Solar Cells. *Energy Environ. Sci.* **2022**, *15* (5), 2096–2107.
- (23) Palmstrom, A. F.; Eperon, G. E.; Leijtens, T.; Prasanna, R.; Habisreutinger, S. N.; Nemeth, W.; Gaubling, E. A.; Dunfield, S. P.; Reese, M.; Nanayakkara, S.; Moot, T.; Werner, J.; Liu, J.; To, B.; Christensen, S. T.; McGehee, M. D.; van Hest, M. F. A. M.; Luther, J. M.; Berry, J. J.; Moore, D. T. Enabling Flexible All-Perovskite Tandem Solar Cells. *Joule* **2019**, *3* (9), 2193–2204.

- (24) Eperon, G. E.; Stone, K. H.; Mundt, L. E.; Schloemer, T. H.; Habisreutinger, S. N.; Dunfield, S. P.; Schelhas, L. T.; Berry, J. J.; Moore, D. T. The Role of Dimethylammonium in Bandgap Modulation for Stable Halide Perovskites. *ACS Energy Lett.* **2020**, *5* (6), 1856–1864.
- (25) Jariwala, S.; Kumar, R. E.; Eperon, G. E.; Shi, Y.; Fenning, D. P.; Ginger, D. S. Dimethylammonium Addition to Halide Perovskite Precursor Increases Vertical and Lateral Heterogeneity. *ACS Energy Lett.* **2022**, *7* (1), 204–210.
- (26) Yoon, S. J.; Kuno, M.; Kamat, P. V. *Shift Happens*. How Halide Ion Defects Influence Photoinduced Segregation in Mixed Halide Perovskites. *ACS Energy Lett.* **2017**, *2* (7), 1507–1514.
- (27) Slotcavage, D. J.; Karunadasa, H. I.; McGehee, M. D. Light-Induced Phase Segregation in Halide-Perovskite Absorbers. *ACS Energy Lett.* **2016**, *1* (6), 1199–1205.
- (28) Barker, A. J.; Sadhanala, A.; Deschler, F.; Gandini, M.; Senanayak, S. P.; Pearce, P. M.; Mosconi, E.; Pearson, A. J.; Wu, Y.; Srimath Kandada, A. R.; Leijtens, T.; De Angelis, F.; Dutton, S. E.; Petrozza, A.; Friend, R. H. Defect-Assisted Photoinduced Halide Segregation in Mixed-Halide Perovskite Thin Films. *ACS Energy Lett.* **2017**, *2* (6), 1416–1424.
- (29) Oliver, R. D. J.; Caprioglio, P.; Peña-Camargo, F.; Buizza, L. R. V.; Zu, F.; Ramadan, A. J.; Motti, S. G.; Mahesh, S.; McCarthy, M. M.; Warby, J. H.; Lin, Y.-H.; Koch, N.; Albrecht, S.; Herz, L. M.; Johnston, M. B.; Neher, D.; Stolterfoht, M.; Snaith, H. J. Understanding and Suppressing Non-Radiative Losses in Methylammonium-Free Wide-Bandgap Perovskite Solar Cells. *Energy Environ. Sci.* **2022**, *15* (2), 714–726.
- (30) Jariwala, S.; Burke, S.; Dunfield, S.; Shallcross, R. C.; Taddei, M.; Wang, J.; Eperon, G. E.; Armstrong, N. R.; Berry, J. J.; Ginger, D. S. Reducing Surface Recombination Velocity of Methylammonium-Free Mixed-Cation Mixed-Halide Perovskites via Surface Passivation. *Chem. Mater.* **2021**, *33* (13), S035–S044.
- (31) Khenkin, M. V.; Katz, E. A.; Abate, A.; Bardizza, G.; Berry, J. J.; Brabec, C.; Brunetti, F.; Bulović, V.; Burlingame, Q.; Di Carlo, A.; Checharoen, R.; Cheng, Y.-B.; Colmann, A.; Cros, S.; Domanski, K.; Duszka, M.; Fell, C. J.; Forrest, S. R.; Galagan, Y.; Di Girolamo, D.; Grätzel, M.; Hagfeldt, A.; von Hauff, E.; Hoppe, H.; Kettle, J.; Köbler, H.; Leite, M. S.; Liu, S.; Loo, Y.-L.; Luther, J. M.; Ma, C.-Q.; Madsen, M.; Mancaeu, M.; Matheron, M.; McGehee, M.; Meitzner, R.; Nazeeruddin, M. K.; Nogueira, A. F.; Odabaşı, Ç.; Osherov, A.; Park, N.-G.; Reese, M. O.; De Rossi, F.; Saliba, M.; Schubert, U. S.; Snaith, H. J.; Stranks, S. D.; Tress, W.; Troshin, P. A.; Turkovic, V.; Veenstra, S.; Visoly-Fisher, I.; Walsh, A.; Watson, T.; Xie, H.; Yıldırım, R.; Zakeeruddin, S. M.; Zhu, K.; Lira-Cantu, M. Consensus Statement for Stability Assessment and Reporting for Perovskite Photovoltaics Based on ISOS Procedures. *Nat. Energy* **2020**, *5* (1), 35–49.
- (32) Eperon, G. E.; Paternò, G. M.; Sutton, R. J.; Zampetti, A.; Haghighirad, A. A.; Cacialli, F.; Snaith, H. J. Inorganic Caesium Lead Iodide Perovskite Solar Cells. *J. Mater. Chem. A* **2015**, *3* (39), 19688–19695.
- (33) Hu, Y.; Aygüler, M. F.; Petrus, M. L.; Bein, T.; Docampo, P. Impact of Rubidium and Cesium Cations on the Moisture Stability of Multiple-Cation Mixed-Halide Perovskites. *ACS Energy Lett.* **2017**, *2* (10), 2212–2218.
- (34) Al-Ashouri, A.; Köhnen, E.; Li, B.; Magomedov, A.; Hempel, H.; Caprioglio, P.; Márquez, J. A.; Morales Vilches, A. B.; Kasparavicius, E.; Smith, J. A.; Phung, N.; Menzel, D.; Grischek, M.; Kegelmann, L.; Skroblin, D.; Gollwitzer, C.; Malinauskas, T.; Jošt, M.; Matič, G.; Rech, B.; Schlattmann, R.; Topić, M.; Korte, L.; Abate, A.; Stannowski, B.; Neher, D.; Stolterfoht, M.; Unold, T.; Getautis, V.; Albrecht, S. Monolithic Perovskite/Silicon Tandem Solar Cell with > 29% Efficiency by Enhanced Hole Extraction. *Science* **2020**, *370* (6522), 1300–1309.
- (35) Rakocevic, L.; Ernst, F.; Yimga, N. T.; Vashishtha, S.; Aernouts, T.; Heumüller, T.; Brabec, C. J.; Gehlhaar, R.; Poortmans, J. Reliable Performance Comparison of Perovskite Solar Cells Using Optimized Maximum Power Point Tracking. *Solar RRL* **2019**, *3* (2), 1800287.
- (36) Bush, K. A.; Frohna, K.; Prasanna, R.; Beal, R. E.; Leijtens, T.; Swifter, S. A.; McGehee, M. D. Compositional Engineering for Efficient Wide Band Gap Perovskites with Improved Stability to Photoinduced Phase Segregation. *ACS Energy Lett.* **2018**, *3* (2), 428–435.
- (37) Frohna, K.; Anaya, M.; Macpherson, S.; Sung, J.; Doherty, T. A. S.; Chiang, Y.-H.; Winchester, A. J.; Orr, K. W. P.; Parker, J. E.; Quinn, P. D.; Dani, K. M.; Rao, A.; Stranks, S. D. Nanoscale Chemical Heterogeneity Dominates the Optoelectronic Response of Alloyed Perovskite Solar Cells. *Nat. Nanotechnol.* **2022**, *17* (2), 190–196.
- (38) Tennyson, E. M.; Frohna, K.; Drake, W. K.; Sahli, F.; Chien-Jen Yang, T.; Fu, F.; Werner, J.; Chosy, C.; Bowman, A. R.; Doherty, T. A. S.; Jeangros, Q.; Ballif, C.; Stranks, S. D. Multimodal Microscale Imaging of Textured Perovskite–Silicon Tandem Solar Cells. *ACS Energy Lett.* **2021**, *6*, 2293–2304.
- (39) El-Hajje, G.; Momblona, C.; Gil-Escrig, L.; Ávila, J.; Guillemot, T.; Guillemoles, J.-F.; Sessolo, M.; Bolink, H. J.; Lombez, L. Quantification of Spatial Inhomogeneity in Perovskite Solar Cells by Hyperspectral Luminescence Imaging. *Energy Environ. Sci.* **2016**, *9* (7), 2286–2294.
- (40) Feldmann, S.; Macpherson, S.; Senanayak, S. P.; Abdi-Jalebi, M.; Rivett, J. P. H.; Nan, G.; Tainter, G. D.; Doherty, T. A. S.; Frohna, K.; Ringe, E.; Friend, R. H.; Sirringhaus, H.; Saliba, M.; Beljonne, D.; Stranks, S. D.; Deschler, F. Photodoping through Local Charge Carrier Accumulation in Alloyed Hybrid Perovskites for Highly Efficient Luminescence. *Nat. Photonics* **2020**, *14* (2), 123–128.
- (41) Yao, J.; Kirchartz, T.; Vezie, M. S.; Faist, M. A.; Gong, W.; He, Z.; Wu, H.; Troughton, J.; Watson, T.; Bryant, D.; Nelson, J. Quantifying Losses in Open-Circuit Voltage in Solution-Processable Solar Cells. *Phys. Rev. Applied* **2015**, *4* (1), 014020.
- (42) Miller, O. D.; Yablonovitch, E.; Kurtz, S. R. Strong Internal and External Luminescence as Solar Cells Approach the Shockley-Queisser Limit. *IEEE J. Photovolt* **2012**, *2*, 303–311.
- (43) Braly, I. L.; deQuilettes, D. W.; Pazos-Outón, L. M.; Burke, S.; Ziffer, M. E.; Ginger, D. S.; Hillhouse, H. W. Hybrid Perovskite Films Approaching the Radiative Limit with over 90% Photoluminescence Quantum Efficiency. *Nature Photon* **2018**, *12* (6), 355–361.
- (44) Stanbery, B. J. Copper Indium Selenides and Related Materials for Photovoltaic Devices. *Critical Reviews in Solid State and Materials Sciences* **2002**, *27* (2), 73–117.
- (45) Wilson, G. M.; Al-Jassim, M.; Metzger, W. K.; Glunz, S. W.; Verlinden, P.; Xiong, G.; Mansfield, L. M.; Stanbery, B. J.; Zhu, K.; Yan, Y.; Berry, J. J.; Ptak, A. J.; Dimroth, F.; Kayes, B. M.; Tamboli, A. C.; Peibst, R.; Catchpole, K.; Reese, M. O.; Klinga, C. S.; Denholm, P.; Morjaria, M.; Deceglie, M. G.; Freeman, J. M.; Mikofski, M. A.; Jordan, D. C.; Tamizhmani, G.; Sulas-Kern, D. B. The 2020 Photovoltaic Technologies Roadmap. *J. Phys. D: Appl. Phys.* **2020**, *53* (49), 493001.
- (46) Barrier, J.; Beal, R. E.; Gold-Parker, A.; Vigil, J. A.; Wolf, E.; Waquier, L.; Weadock, N. J.; Zhang, Z.; Schelhas, L. T.; Nogueira, A. F.; McGehee, M. D.; Toney, M. F. Compositional Heterogeneity in $\text{Cs}_{1-x}\text{FA}_x\text{Pb}(\text{Br}_{1-x}\text{I}_x)_3$ Perovskite Films and Its Impact on Phase Behavior. *Energy Environ. Sci.* **2021**, *14* (12), 6394–6405.
- (47) Mundt, L. E.; Zhang, F.; Palmstrom, A. F.; Xu, J.; Tirawat, R.; Kelly, L. L.; Stone, K. H.; Zhu, K.; Berry, J. J.; Toney, M. F.; Schelhas, L. T. Mixing Matters: Nanoscale Heterogeneity and Stability in Metal Halide Perovskite Solar Cells. *ACS Energy Lett.* **2022**, *7* (1), 471–480.
- (48) Macpherson, S.; Doherty, T. A. S.; Winchester, A. J.; Kosar, S.; Johnstone, D. N.; Chiang, Y.-H.; Galkowski, K.; Anaya, M.; Frohna, K.; Iqbal, A. N.; Nagane, S.; Roose, B.; Andaji-Garmaroudi, Z.; Orr, K. W. P.; Parker, J. E.; Midgley, P. A.; Dani, K. M.; Stranks, S. D. Local Nanoscale Phase Impurities Are Degradation Sites in Halide Perovskites. *Nature* **2022**, *607* (7918), 294–300.
- (49) Bercegol, A.; Ramos, F. J.; Rebai, A.; Guillemot, T.; Puel, J.-B.; Guillemoles, J.-F.; Ory, D.; Rousset, J.; Lombez, L. Spatial Inhomogeneity Analysis of Cesium-Rich Wrinkles in Triple-Cation Perovskite. *J. Phys. Chem. C* **2018**, *122* (41), 23345–23351.
- (50) Braunger, S.; Mundt, L. E.; Wolff, C. M.; Mews, M.; Rehmann, C.; Jošt, M.; Tejada, A.; Eisenhauer, D.; Becker, C.;

Guerra, J. A.; Unger, E.; Korte, L.; Neher, D.; Schubert, M. C.; Rech, B.; Albrecht, S. $\text{Cs}_x\text{FA}_{1-x}\text{Pb}(\text{I}_{1-y}\text{Br}_y)_3$ Perovskite Compositions: The Appearance of Wrinkled Morphology and Its Impact on Solar Cell Performance. *J. Phys. Chem. C* **2018**, *122* (30), 17123–17135.

(51) Bush, K. A.; Rolston, N.; Gold-Parker, A.; Manzoor, S.; Hausele, J.; Yu, Z. J.; Raiford, J. A.; Cheacharoen, R.; Holman, Z. C.; Toney, M. F.; Dauskardt, R. H.; McGehee, M. D. Controlling Thin-Film Stress and Wrinkling during Perovskite Film Formation. *ACS Energy Lett.* **2018**, *3* (6), 1225–1232.

(52) Kim, S.-G.; Kim, J.-H.; Ramming, P.; Zhong, Y.; Schötz, K.; Kwon, S. J.; Huettner, S.; Panzer, F.; Park, N.-G. How Antisolvent Miscibility Affects Perovskite Film Wrinkling and Photovoltaic Properties. *Nat. Commun.* **2021**, *12* (1), 1554.

(53) Hu, M.; Bi, C.; Yuan, Y.; Bai, Y.; Huang, J. Stabilized Wide Bandgap $\text{MAPbBr}_{1-x}\text{I}_x$ Perovskite by Enhanced Grain Size and Improved Crystallinity. *Advanced Science* **2016**, *3* (6), 1500301.

(54) Knight, A. J.; Wright, A. D.; Patel, J. B.; McMeekin, D. P.; Snaith, H. J.; Johnston, M. B.; Herz, L. M. Electronic Traps and Phase Segregation in Lead Mixed-Halide Perovskite. *ACS Energy Lett.* **2019**, *4* (1), 75–84.

(55) Gratia, P.; Zimmermann, I.; Schouwink, P.; Yum, J.-H.; Audinot, J.-N.; Sivula, K.; Wirtz, T.; Nazeeruddin, M. K. The Many Faces of Mixed Ion Perovskites: Unraveling and Understanding the Crystallization Process. *ACS Energy Lett.* **2017**, *2* (12), 2686–2693.

(56) Stoumpos, C. C.; Mao, L.; Malliakas, C. D.; Kanatzidis, M. G. Structure–Band Gap Relationships in Hexagonal Polytypes and Low-Dimensional Structures of Hybrid Tin Iodide Perovskites. *Inorg. Chem.* **2017**, *56* (1), 56–73.

(57) Weber, O. J.; Marshall, K. L.; Dyson, L. M.; Weller, M. T. Structural Diversity in Hybrid Organic–Inorganic Lead Iodide Materials. *Acta Crystallographica Section B* **2015**, *71* (6), 668–678.

(58) Seth, C.; Khushalani, D. Non-Perovskite Hybrid Material, Imidazolium Lead Iodide, with Enhanced Stability. *ChemNanoMat* **2019**, *5* (1), 85–91.

(59) Li, Z.; Wang, X.; Wang, Z.; Shao, Z.; Hao, L.; Rao, Y.; Chen, C.; Liu, D.; Zhao, Q.; Sun, X.; Gao, C.; Zhang, B.; Wang, X.; Wang, L.; Cui, G.; Pang, S. Ammonia for Post-Healing of Formamidinium-Based Perovskite Films. *Nat. Commun.* **2022**, *13* (1), 4417.

(60) Wang, X.; Fan, Y.; Wang, L.; Chen, C.; Li, Z.; Liu, R.; Meng, H.; Shao, Z.; Du, X.; Zhang, H.; Cui, G.; Pang, S. Perovskite Solution Aging: What Happened and How to Inhibit? *Chem.* **2020**, *6* (6), 1369–1378.

(61) Ferm, R. J.; Riebsomer, J. L. The Chemistry of the 2-Imidazolines and Imidazolidines. *Chem. Rev.* **1954**, *54* (4), 593–613.

Recommended by ACS

Van der Waals Force-Assisted Heat-Transfer Engineering for Overcoming Limited Efficiency of Flexible Perovskite Solar Cells

Oh Yeong Gong, Hyun Suk Jung, *et al.*

AUGUST 08, 2022
ACS ENERGY LETTERS

READ 

F-Type Pseudo-Halide Anions for High-Efficiency and Stable Wide-Band-Gap Inverted Perovskite Solar Cells with Fill Factor Exceeding 84%

Junlei Tao, Shaopeng Yang, *et al.*

JULY 07, 2022
ACS NANO

READ 

FAPbI₃ Perovskite Films Prepared by Solvent Self-Volatilization for Photovoltaic Applications

Qiqi Zhang, Qilin Dai, *et al.*

FEBRUARY 02, 2022
ACS APPLIED ENERGY MATERIALS

READ 

Efficient and Stable FAPbBr₃ Perovskite Solar Cells via Interface Modification by a Low-Dimensional Perovskite Layer

Yawen Liu, Erik M. J. Johansson, *et al.*

SEPTEMBER 16, 2021
ACS APPLIED ENERGY MATERIALS

READ 

Get More Suggestions >