Soft Matter



REVIEW

View Article Online
View Journal



Cite this: DOI: 10.1039/d3sm00090g

Assembly and manipulation of responsive and flexible colloidal structures by magnetic and capillary interactions

Abhirup Basu, (1) † Lilian B. Okello, (1) † Natasha Castellanos, Sangchul Roh (1) ‡ and Orlin D. Velev (1) *

The long-ranged interactions induced by magnetic fields and capillary forces in multiphasic fluid-particle systems facilitate the assembly of a rich variety of colloidal structures and materials. We review here the diverse structures assembled from isotropic and anisotropic particles by independently or jointly using magnetic and capillary interactions. The use of magnetic fields is one of the most efficient means of assembling and manipulating paramagnetic particles. By tuning the field strength and configuration or by changing the particle characteristics, the magnetic interactions, dynamics, and responsiveness of the assemblies can be precisely controlled. Concurrently, the capillary forces originating at the fluid-fluid interfaces can serve as means of reconfigurable binding in soft matter systems, such as Pickering emulsions, novel responsive capillary gels, and composites for 3D printing. We further discuss how magnetic forces can be used as an auxiliary parameter along with the capillary forces to assemble particles at fluid interfaces or in the bulk. Finally, we present examples how these interactions can be used jointly in magnetically responsive foams, gels, and pastes for 3D printing. The multiphasic particle gels for 3D printing open new opportunities for making of magnetically reconfigurable and "active" structures.

Received 23rd January 2023, Accepted 2nd March 2023

DOI: 10.1039/d3sm00090g

rsc.li/soft-matter-journal

Department of Chemical and Biomolecular Engineering, North Carolina State University, Raleigh, NC 27695, USA. E-mail: odvelev@ncsu.edu

- † Both authors contributed equally.
- ‡ School of Chemical Engineering, Chonnam National University, Gwangju 61186, Republic of Korea.

1. Introduction

The assembly of colloidal particles is generally categorized into two broad classes: self and directed assembly. Self-assembly can occur spontaneously due to intrinsic specific interactions



Abhirup Basu

Abhirup Basu is a third year PhD student in the department of Chemical & Biomolecular Engineering at NC State University. He received his BE (Honors) and master's degrees in Chemical Engineering from Jadavpur University (2015) and Indian Institute of Technology Bombay, India (2017) respectively. He worked as a research officer in the R&D division at Tata Steel Ltd. India for two years before joining Velev group for his PhD

studies. His current research focus is in the areas of directed assembly of paramagnetic colloidal particles and finding their applications as active particles directed by electric and magnetic fields.



Lilian B. Okello

Lilian B. Okello is a final year PhD student in the department of Chemical & Biomolecular Engineering at NC State University. She earned her Bachelor's and Master's degrees in Chemical Engineering at The Grove School of Engineering, The City College of The City University of New York in Manhattan, NYC. Additionally, she earned a Master's degree in Sustainability at CUNY before joining the Velev Research Group. Her research

focus has been to synthesize and engineer the properties of silicone-based multiphasic homocomposite capillary pastes for 3D printing of soft magnetically responsive actuators.

in natural systems to form large scale structures such as lipid bilayers around live cells, micelles from surfactants, and DNA hybridization from complimentary strands of nucleotides.³ However, most interactions on colloidal scale such as van der Waals, electrostatic and steric repulsion are unidirectional and lack specificity. Colloidal assemblies whose formation is driven by such conventional colloidal forces are commonly governed by minimization of interparticle interaction energy, or maximization of the entropy of the system.4 One of the simplest approaches to colloidal assembly is the restriction of the volume, or drying of the suspensions, typically leading to the



Natasha Castellanos

Dr Natasha Castellanos is currently a Research & Development Scientist at Phase Change Energy Solutions. She graduated with a Bachelor of Science in Chemistry and Mathematics from Salem College in 2016. She then went on to earn a Master of Science (2018) and PhD in Chemical Engineering (2021) from NC State University under the guidance of Dr Orlin D. Velev. Her dissertation comprised research on smart colloid compo-

sites, magnetocapillary gels and interactions, and homocomposite 3D printing. Her current research focus is formulation development of phase change energy smart materials.

formation of isotropic close packed 2D or 3D crystals.⁵⁻⁸ Such assembly processes have been a focus of research interest as, for example, they allow to model some of the fundamentals in the atomistic level crystallization and defect formation. However, they are limited in their ability to form complex directionally oriented structures.9

Directional colloidal assembly techniques using external fields such as magnetic fields, 10-13 electric fields 14-17 and light 18,19 offer efficient ways of overriding the common colloidal interactions and guiding the particles to form out-of-equilibrium structures by accelerating the assembly kinetics. Further, external fields offer more precise control of the dynamics of the assembly process by changing the field parameters and can be used to assemble structures ranging from oriented 2D crystals,20 nanowires, 21 electro and magnetorheological fluids to other stimuli responsive materials.²² By tuning the field parameters, researchers are able to form multiple structural patterns that can be re-configured on-demand. 9,23,24 Additional complexity and directionality of the assemblies can be achieved by using patchy and shaped colloidal particles which are anisotropic in geometry, polarizability, or surface properties.^{25–27}

The goal of this review is to summarize the rich variety of ways in which the field-driven assembly can be combined with multiphasic systems and capillary forces to form numerous classes of flexible responsive soft matter. The topics that are reviewed are schematically presented in Fig. 1. First, we briefly introduce the fundamentals of magnetic interactions between isotropic colloidal particles, and the principles of magnetic field-directed assembly of structures in multiple dimensions (Fig. 1a). This assembly is a convenient tool for making directionally responsive structures where the particles form



Sangchul Roh

Dr Sangchul Roh is presently an assistant professor in the School of Chemical Engineering at Chonnam National University, South Korea. He earned his PhD degree from NC State University, USA (2019). His PhD dissertation under the guidance of Prof. Orlin D. Velev is on 3D printing, liquidliquid nanofabrication, and novel soft composites. After a postdoc at Cornell University, he joined Chonnam National University in 2023. His research interests

encompass viscoelastic materials, structured soft matter systems, and polymer composites.



Orlin D. Velev

Dr Orlin Velev is a Frank and Doris Culberson Distinguished Professor at NC State University. He received his PhD degree from the University of Sofia, Bulgaria (1996), while also performing research for one year in Japan. After a postdoc at the University of Delaware, Velev joined NC State University in 2001. Velev has contributed more than 235 publications and has presented more than 300 invited presentations. His numerous awards

include NSF Career, AIChE Andreas Acrivos Award for Professional Progress and ACS Langmuir Lecturer. Velev has been elected to an ACS Fellow and MRS Fellow. He has established a record of innovative research in the assembly of colloidal nanostructures with electrical and photonic functionality, biosensors, microfluidics and nanomanufacturing. Velev has been the first to synthesize "inverse opals" and has pioneered novel nanoparticle materials, Janus and special shape active particles and biopolymer nanostructures.

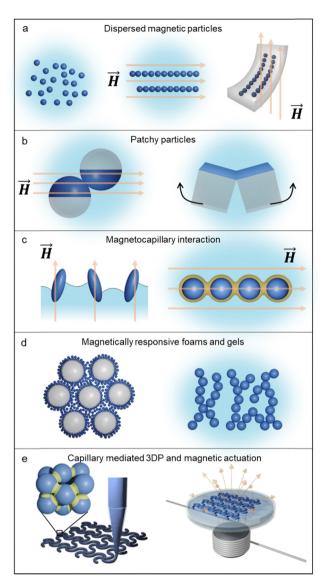


Fig. 1 Highlights of the perspective review: (a) magnetic field guided assembly of isotropic colloidal particles dispersed in a liquid medium or embedded in a polymer matrix; (b) responsive structures assembled by anisotropic or "patchy" particles, for example, Janus spheres (left) and one-sided metal coated patchy microcubes (right); (c) interactions guided by magnetic field in conjunction with capillarity at interfaces (left) and in the bulk (right); (d) assembly of magnetically responsive foams (left) and gels (right); (e) capillary-mediated 3D printing (left) and magnetic actuation of soft matter (right).

large-scale hierarchical assemblies ranging from chains to sheets, to bundles and clusters (Fig. 1a and b). The magnetic field guided structuring is robust, rapid and is initiated and controlled outside the system without interfering with experimental parameters such as temperature, pH and solvent composition. $^{28\mbox{-}30}$ We discuss how multiaxial fields such as biaxial (rotating) or triaxial (precessing) ones introduce extra control parameters, which enable the assembly of a wide variety of complex morphologies. 31,32 Next, we extend these principles to probe into the recent advancements made in the assembly of magnetically reconfigurable structures using anisotropic or patchy particles (Fig. 1b).

The second group of topics in this perspective is how capillary forces provide another convenient set of techniques to control and manipulate particle structures. Colloidal particles adsorbed or protruding through fluid-fluid interfaces (liquid-air, or liquid-liquid) can experience capillary forces due to the deformation of the interface around them.33-35 These forces are characterized by very long range and directionality, and can be attractive or repulsive depending on the shape of the meniscus between the particles. Alternatively, small amount of liquid can result in capillary bridging between particles and completely change the rheological properties of the suspension (Fig. 1c). We further discuss how capillary interactions on the colloidal scale can be used in conjunction with magnetic fields to restructure various multiphasic colloidal systems, 36-40 resulting in magneto-capillary gels, foams and coatings (Fig. 1d). A few classes of systems of specific interest include capillary pastes and gels for 3D printing (Fig. 1e), which we discuss separately due to their large importance and diversity of applications. We conclude with a summary of the opportunities and perspectives for further research that can be conducted in this area.

2. Assembly of colloidal particles via magnetic interactions

The availability of efficient means to generate magnetic fields in space and time has enabled a broad range of scientific investigations of the directed magnetic assembly of colloidal structures. Magnetic field induce polarization in the colloidal particles the extent of which is dependent on the orientation of the magnetic moments inside the material domains. In short, magnetic materials are classified broadly into three types: (i) paramagnetic, which have randomly oriented magnetic moments and align themselves along the field, but lose their magnetism upon removal of the field, (ii) diamagnetic where the atoms have no magnetic moments and are weakly repelled by an applied magnetic field, (iii) ferromagnetic, which are analogous to paramagnetic ones but contain permanently aligned magnetic moments and retain residual magnetization after the field is switched off. Amongst the various types of magnetic particles, superparamagnetic particles, mostly found in the size range of 3-50 nm are widely used for field-directed assembly because of their high magnetic susceptibility. Since each superparamagnetic particle contains a single magnetic domain, the polarized particles can be approximated as a point dipole. The interaction potential when the interparticle separation is much larger than the particle diameter (Fig. 2a) between two dipoles $\overrightarrow{\mu_1}$ and $\overrightarrow{\mu_2}$ separated by a distance of r_{12} is given by

$$U_{12} = \frac{1}{r_{12}^3} \left[\overrightarrow{\mu_1} \cdot \overrightarrow{\mu_2} - 3 \frac{\left(\overrightarrow{\mu_1} \cdot \overrightarrow{r_{12}} \right) \left(\overrightarrow{\mu_2} \cdot \overrightarrow{r_{12}} \right)}{r_{12}^2} \right]. \tag{1}$$

The simplest way of structuring such colloidal particles is the application of a static uniform magnetic field, which aligns the particles along the direction of their magnetic moments. The magnetically polarized particles attract or repel each other Review

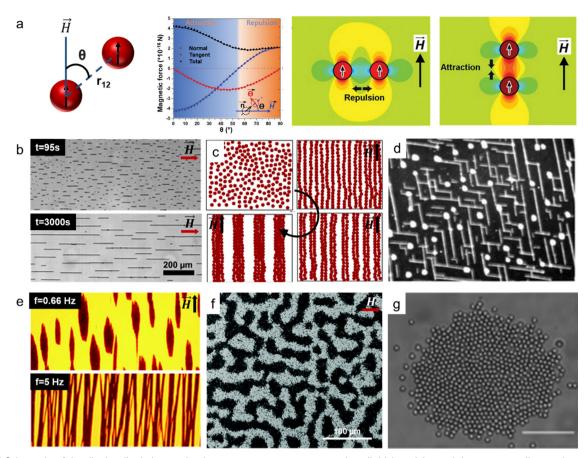


Fig. 2 (a) Schematic of the dipole-dipole interaction between two superparamagnetic colloidal particles and the corresponding total magnetic force with tangential and normal components as a function of the angle between them. It also shows the two limiting cases of magnetic interaction when the particles are oriented at 90° (side by side) and 0° (head-to-tail). Reproduced with permission from ref. 24 and 29. Copyright 2020, Wiley-VCH and 2013, Elsevier. (b) Optical snapshots of superparamagnetic colloidal particles forming linear chains and their growth in the presence of a uniaxial static magnetic field. Reproduced with permission from ref. 43. Copyright 2015, American Institute of Physics. (c) Lateral zipping of chains to form thick bundles in magnetic nanofluids under external magnetic fields. The arrow represents the increase in critical magnetic fields. Reproduced with permission from ref. 52. Copyright 2009, American Physical Society. (d) A network of linear structures with T-, L-, and "criss-cross" junctions under combined AC/DC magnetic fields. Reproduced with permission from ref. 53. Copyright 2011, American Chemical Society. (e) Magnetic field induced assembly into condensed (top) or percolated (bottom) structures from paramagnetic colloidal particles after applying pulsed magnetic fields at different frequencies. Reproduced with permission from ref. 55. Copyright 2014, Royal Society of Chemistry. (f) Phase separation followed by aggregation of paramagnetic particles into spinoidals after applying a high frequency rotational magnetic field. Reproduced with permission from ref. 70. Copyright 2020, Royal Society of Chemistry. (q) Optical micrograph of packed cluster with hexagonal ordering of paramagnetic carboxyl-coated polystyrene particles in a high frequency rotating magnetic field. Reproduced with permission from ref. 69. Copyright 2018, American Physical Society.

depending on the mutual orientation of their dipoles. For two identical dipoles, the above equation can be simplified to

$$U_{12} = \frac{\mu^2}{r_{12}^3} [1 - 3\cos^2\theta]. \tag{2}$$

The attractive dipolar interaction is maximal when the particles are aligned in a "head to tail" configuration, i.e., $\theta = 0^{\circ}$ (Fig. 2a). Provided that the interparticle potential is strong enough to overcome thermal fluctuations, this leads to the formation of 1D linear chains, which represent the simplest hierarchy of the directed assembly. With the increase in angle between the particles, this attractive force decreases and vanishes at a "magic" angle of 54.7°, above which the particles encounter a repulsive force. 29,41 The rate of chain assembly is further dependent on the particle volume fraction and the effective capture radius, which is defined as the threshold interparticle distance at which the attractive potential is equal to the thermal energy kT. 42 Particles at greater distances apart rely on diffusion to enter into the capture radius. Fig. 2b shows snapshots of the aggregation of superparamagnetic polystyrene particles from a Brownian fluid system after applying a uniaxial magnetic field for 3000 s.43 The cluster growth rate was found to vary monotonically with the particle packing fractions and magnetic field strength. The cluster size length followed a scaling relationship of $\langle L \rangle = f\left(\phi^{\frac{3}{2}}B^2t\right)$ where $\langle L \rangle$ defines the mean cluster size length, and ϕ , B and t represent packing fraction, field strength, and time of application of the magnetic field, respectively. The assemblies from superparamagnetic particles can disassemble or break apart upon removal of the

field owing to their negligible residual magnetization. These assemblies and their field responsiveness can be preserved by embedding them inside soft polymer matrix^{44–46} or physically or chemically binding the nanoparticles into flexible structures, 47-49 which will be discussed in the next sections.

The linear chains from magnetic colloidal particles can also coalesce laterally and form thick fibers (bundles) or crosslinked networked structures. 50,51 By calculating the interaction energy between lateral chains, Furst and Gast predicted that at shorter separation between two chains there exists either a repulsive or attractive potential depending on their mutual alignment.⁵¹ The potential will be attractive if the chains are out of registry, and will be repulsive if the chains are in registry. As the field strength is increased, two chains can interact laterally at a critical field strength to overcome the energy barrier for lateral aggregation.⁵² After coalescing laterally, the overall energy of the system drops, and the aggregation into bundles gets repeated at the next critical field strength (Fig. 2c). One can observe further complex and structurally different network formation by applying more complex field configurations. For instance, linear networked structures comprised of T-, L- and "criss-cross" junctions can be assembled from paramagnetic colloidal particles by using alternating current (AC) and direct current (DC) magnetic fields orthogonal to each other (Fig. 2d).⁵³ Further, disc-like clusters can be formed at the network junctions by increasing the frequency of the oscillating field.

Paramagnetic colloidal particles can also condense into crystalline structures in pulsating magnetic fields. 54,55 Swan et al. studied the depercolation and crystallization of polystyrene latex beads with embedded iron oxide magnetic nanoparticles under toggled magnetic fields as a function of the frequency and applied field strength. They showed that a uniform pulsed field could be used to organize the disordered suspension into entangled chains (Fig. 2e). While operating at frequencies lower than the relaxation time of the suspensions, the structures lost their "memory" at every pulse and reorganized themselves. However, at higher frequencies, the field-off portion of the pulse was so short that the assemblies could not overcome the kinetic constraints typical of strong dipolar interactions and self-assembled to condensed crystalline domains. Other condensed phases including close-packed hexagonal, square, labyrinth and honeycomb phases can be observed experimentally by using soft-core repulsive magnetic colloidal particles in presence of a transverse magnetic field, 56 in agreement with simulation results by other research groups. 57,58 Their spatial arrangement can be conveniently tuned by varying the particle density.

Complex hierarchical structures can be formed with such longitudinal assemblies if the static field is replaced by timeand space-varying magnetic fields, one of the simplest of which is the rotating magnetic field. 47,59,60 Magnetic and viscous forces are the two major factors governing this assembly dynamics in such fields. Earlier simulation studies showed that in contrast to the uniaxial fields, which drive the formation of chain-like structures, rotating fields could induce the organization of polarizable particles into sheet-like structures.⁶¹⁻⁶³

In reality, the chains undergo steady rotation at low field frequencies due to the magnetic torque, while viscous forces prevent their complete alignment and lead to the rotation of the chains with a phase lag angle. The phase lag angle increases with the increase of the length of the chains, which may result in their fragmentation. 64,65

Further complexity can be introduced by precessing fields combining a static magnetic field around a particular axis (for example z-axis) with an orthogonal rotating magnetic field (x-y plane). In the presence of a precessing rotating magnetic field, the linear chains can buckle and transform into various configurations such as a dynamic helix, hairpin, S-shaped chain or others. 66,67 The chains can further break up at multiple points depending on the field rotation rate and can collapse into two-dimensional clusters in the case of very high-frequency rotating fields. 68,69 Hilou et al. observed the phase transition of a homogenous colloidal suspension to a bicontinuous phase and the formation of spinoidal microstates in the time-varying fields (Fig. 2f). 70 While the clusters are loosely packed without ordered structures seen at low field strength, they can finally form colloidal crystals with hexagonal ordering with increase in field strength (Fig. 2g).⁶⁹ Osterman et al. predicted that this cluster formation is achieved due to long-range attractive potential between the particles in a precessing field.³² Conversely, isotropic repulsive potential can also help in achieving ordered crystals with large interparticle spacings as compared to the crystals formed with attractive dipolar interactions. Thus, the magnetic interactions enable assembly on many length scales.

3. Magnetic interactions and structures from anisotropic colloidal particles

Anisotropic colloidal particles are rapidly emerging topic of colloidal and materials research, partially due to the large diversity of structures that can be synthesized through their directed assembly. The anisotropy can originate from particle shape but can also be a result of surface modification.⁷¹⁻⁷⁴ In order to incorporate shape or surface anisotropy, numerous microfabrication techniques including photolithography, soft lithography, microfluidics and micromolding have been used to form patches of dissimilar charges, polarizability, or different functional groups attached to the particle surface. 75-80 The simplest class of such particles are hemispherically different "Janus microspheres", which have been fabricated and investigated widely in the assembly of hierarchical structures for both fundamental and industrial applications. 14,81,82 Many of the originally produced Janus particles have a metallic coating on one hemisphere of a polystyrene particle and a dielectric part on the other hemisphere and can vary in size from 100 nm to millimiters. 74,83,84 An anisotropic magnetic component can be introduced by metal vapor deposition of a thin magnetic film on the particle surface. Alternatively, magnetic nanoparticles can be attached to a portion of non-magnetic patchy

particle by selective adsorption, taking advantage of the particle's differentiated surface properties.⁸⁵

Upon switching on the magnetic field, the randomly oriented metallo-dielectric Janus particles can be assembled into "staggered" chains, aligned along the direction of the magnetic field. The orientation of the particles in the chains is guided by the strong interaction between the polarized metallic halves. The alignment of the dipoles in the metal leads to the staggered packing with the metal halves facing each other in alternate directions (Fig. 3a). 10,14,86 The disassembly

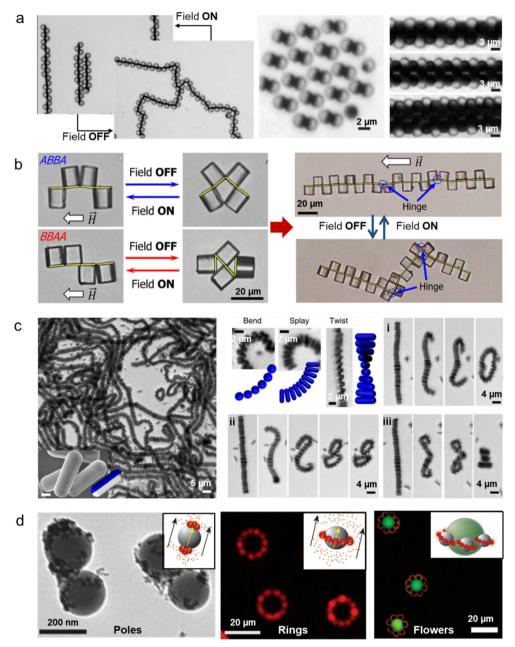


Fig. 3 Reconfigurable structures guided by magnetic field: (a) linear double chains (left), dumbbell shaped dimers (middle) and microtubules (right) assembled from Janus spheres under the influence of uniaxial, rotating and precessing magnetic fields respectively. In the first case, the chains do not disassemble after switching off the field because of residual magnetization and may fold at various hinge points. Reproduced with permission from ref. 10, 87 and 88. Copyright 2009, Royal Society of Chemistry, 2014, Wiley-VCH and 2012, Nature. (b) Patchy microcubes with a metallic coating on one side form two open configurations with the metal side facing each other or the metal side parallel to each other. The structures can reversibly open and close by toggling on and off the field. The cubes can form long linear chains in a concentrated system and can bend at suitable hinges upon switching off the field. Reproduced with permission from ref. 11. Copyright 2017, AAAS. (c) Optical micrograph of dipolar "Janus" rods forming colloidal ribbons (left) in uniform magnetic field. Modes of deformation of the ribbons and formation of cyclic structures upon reversing the direction of the field (right). Reproduced with permission from ref. 93. Copyright 2013, Nature, (d) colloidal superstructures with multipole symmetry from diamagnetic (grey spheres) and paramagnetic (red spheres) particles in a magnetized ferrofluid medium (brown dots). Reproduced with permission from ref. 30. Copyright 2009, Nature.

kinetics of these chains after switching off the magnetic field depend on the attraction of the neighboring particle by residual magnetic polarization, which in turn is a function of the thickness of the deposited metallic layer. For example, chains of "Janus" particles with a coating thickness of 8 nm came apart easily by small shear forces; while those with a coating thickness of 34 nm maintained their structures and could be disassembled only after demagnetization. Further, replacing the uniaxial field with other fields completely changes the assembly configuration. In particular, the "Janus" particles self-organized to produce hexagonal crystals under a rotating field of moderate strength with the metal coating pointing perpendicular to the plane of the field.³¹ The constituent particles were found to rotate synchronously with the field. An increase in the field strength in this system formed new structures where the magnetic hemispheres of "Janus" particle pairs faced each other to form dumbbell-like clusters (Fig. 3a middle).87 Another time-dependent configuration using a precessing field causes the Janus particles to assemble into microtubules, 88 and stack as polygons (Fig. 3a right). These particles also rotated in place but maintained the overall orientation and the structural integrity of the microtubes.

The use of shape-anisotropic particles also leads to the formation of chains and arrays of unusual symmetries. The localized dipole interactions and torque acting on the particles determine their orientation when the field is applied during the assembly process. Particle anisotropy also brings additional steric components, which directs the symmetry of assemblies and is also governed by the size and shape of the patches. 89,90 For example, doublets of two differently sized silica particles with a magnetic cap self-assemble into helical structures as a result of steric hindrance induced by the size differences. Further, polymer microcubes with a metallic coating on one side11,12,91 or microcylinders with a metallic coating on one half⁷⁹ form straight or staggered linear chains in static magnetic field (Fig. 3b). Our group has shown that the magnetic patches of such particles acquired a dipole which led to cube chain assembly parallel to the applied magnetic field.¹¹ In essence, the metal coated face acts as a structural director for the microcube assembly, and the local orientation of particles in the chains depends on the mutual interactions between the metal patches. Two adjacent cubes in a sequence can form cis- or trans-configurations where the metallic side can be aligned side by side or top-to-tail, respectively. These configurations correspond to two minima of the potential energy landscape. After the removal of the magnetic field, the particles retain residual magnetization and interactions, so that the microcube chains demonstrate active dynamic rearrangement of the assembled chains into bundled or partially wrapped configurations. As a result, these microcube chains can stretch and contract reversibly by switching on and off the magnetic field. The repetitive opening and closing of small "microscallop" clusters of magnetic microcubes immersed in non-Newtonian fluid can be used for their directional active propulsion.92 The ability of these soft robotic devices to

reconfigure on-demand can find applications such as novel microrheometers, microswimmers or microbots for biological applications.91

Other types of complex structures that have been reported use magnetostatic interactions of colloidal silica rods coated with a magnetic layer on one hemicylinder (Fig. 3c). 93 These Janus rods were assembled into ribbons perpendicular to the applied field and were held in position even after field removal. These assemblies are also capable of undergoing deformations such as bending, buckling, and twisting and can be controllably reconfigured from ribbons to closed cyclic structures by reversing the direction of the field. The right panel of Fig. 3c shows the evolution of rings by three major pathways where the ribbons either curve and the chain ends meet, or the ribbons split into fragments when the field reversal is very rapid. The ribbons could also stand vertically on a substrate in the presence of a relatively weak vertical magnetic field.

Finally, combining colloidal particles of unequal polarizability can also lead to the formation of various superstructures. Hierarchically assembled structures have been formed by applying a uniform field to a multicomponent suspension of diamagnetic and paramagnetic particles within a ferrofluid.30 Here, the paramagnetic particles are attracted either towards the equator or towards the poles of the non-magnetic particles depending on the concentration of the ferrofluid, resulting in the formation of "rings" or "poles" (Fig. 3d). In a 4-component system comprising of paramagnetic and two different sized non-magnetic particles in a ferrofluid, multipolar assemblies resembling axial octupoles ('flowers'), and mixed multipole arrangements ('two tone') have been observed. In another method, a ferrofluid suspension of patchy anisotropic particles with non-magnetic polystyrene particles showed that the latter particles aligned with the metallic core of the patchy particle diamagnetically.13 Such assembly can be reversed on-demand by switching the field on and off, while permanent superstructures can be synthesized by replacing the surface coating of the non-magnetic particles with crosslinkable amino groups.

4. Capillary mediated interaction and assembly

Capillary interactions present another powerful set of tools for assembling colloidal arrays and clusters. These interactions arise when colloidal particles partially wetted by liquid seek to minimize the energy of the liquid interface deformed around them.94 Unlike smooth particles, surface roughness, defects, chemical composition variation, or other sources of pinned contact line in spheroidal and complex-shaped particles lead to complex undulated interface distortions. 33,95 Non-spherical particles can further create undulated contact line even in absence of rough surface or chemical composition variation. 96-99 Different classes of capillary phenomena resulting from such deformations were originally classified and analyzed in a series of seminal papers by Kralchevsky and coworkers. 100-102 The capillary interactions between particles are broadly classified

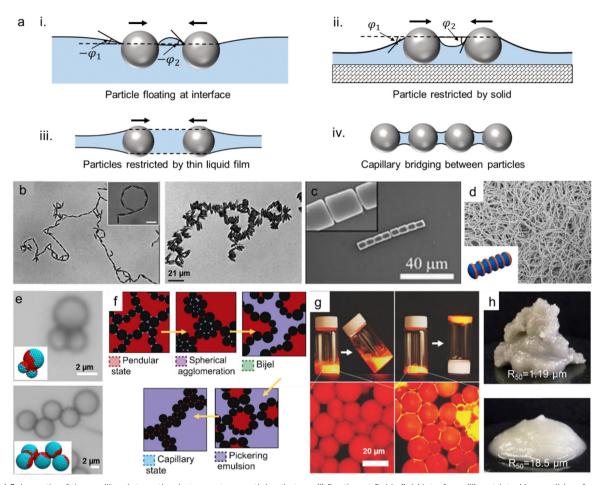


Fig. 4 (a) Schematic of the capillary interaction between two particles that are (i) floating at fluid-fluid interface, (ii) restricted by a solid surface from the bottom, (iii) confined in a thin 2D liquid film, and (iv) capillary bridging pulling them together. Capillary assembly of shaped anisotropic colloids: (b) polystyrene ellipsoids forming tip-to-tip and silica ellipsoids forming side-to-side configurations at oil-water interface. Reproduced with permission from ref. 113. Copyright 2005, American Physical Society. (c) Chains of SU-8 cylinders at an oil-water interface. Reproduced with permission from ref. 114. Copyright 2010, American Chemical Society. Capillary assembly of patchy particles via capillary bridging: (d) long colloidal chains formed from polystyrene discs with two liquid patches. Reproduced with permission from ref. 115. Copyright 2019, American Chemical Society. (e) 3D and 2D architectures assembled from "Janus" microspheres (top) and double patched microspheres (down). Reproduced with permission from ref. 116. Copyright 2016, American Chemical Society. (f) Schematics of different particle-liquid-liquid systems with increasing volume fraction of preferentially wetting liquid. The two extremes, i.e., the pendular state and the capillary state represent capillary suspensions. Reproduced with permission from ref. 117. Copyright 2014, Elsevier Ltd. (g) "Homocomposite" capillary paste prepared from PDMS beads in liquid-like suspension (right), which gels after adding liquid PDMS precursor bridging the beads (right). Reproduced with permission from ref. 118. Copyright 2017, Wiley-VCH. (h) Effect of particle size on the rheological properties of capillary suspensions. Reproduced with permission from ref. 119. Copyright 2012, Royal Society of Chemistry.

into three classes illustrated in Fig. 4a. In the first case, two particles floating on a liquid surface deform the flat interface due to gravity (Fig. 4ai), acting against the interfacial tension of the liquid. This interfacial deformation makes the particles approach each other to reduce the overall interfacial and gravitational potential energies. While the particle weight plays the governing role in the origin of capillary forces between floating particles, the interaction can be driven by the wetting of the solid surface by the liquid as seen in the next two cases of particles confined in thin films (Fig. 4aii and iii). The interactions in this case are strongly affected by the magnitude of surface tension and the contact angle between the liquid and the particles. The former is called flotation forces, while the second one is called lateral immersion forces. 100,103 In the case of immersion forces, the particles are either restricted by a solid substrate at the bottom (Fig. 4aii) or confined in a thin liquid film joining the two particles (Fig. 4aiii). The flotation force between two spherical particles of the same size is approximately proportional to r^6 , while the immersion force is proportional to r^2 , where r is the radius of the particle. ¹⁰⁴ For floating particles, the competition between the thermal forces and the interfacial forces becomes prominent as we move from micron scale to nanoscale, leading to the instability of the assembled structures with nanoparticles because of thermal fluctuations. 105,106 However, in case of immersion forces, the thermal energy is usually lower than the interfacial energy by several orders of magnitude, so that both microparticles and nanoparticles confined on a solid surface can interact strongly. It is

useful to note in this context that the capillary forces in thin wetting films are not the major origin of evaporative particle assembly as frequently assumed, as the latter is primarily driven by the convective transport of colloidal particles due to evaporation of water. 107,108

The flotation and immersion forces can be attractive or repulsive depending on the curvature of the liquid menisci, *i.e.*, they are attractive when $\sin \varphi_1 \sin \varphi_2 > 0$ and they are repulsive when $\sin \varphi_1 \sin \varphi_2 < 0$. In addition to abovementioned two types of capillary forces, there is a distinct third class of capillary "bridging forces", where the particles come into contact while bound by small volume of liquid (Fig. 4aiv). Mechanistically, capillary bridging forces act normal to the line of contact of the particle surface, whereas the capillary flotation and immersion forces act tangential to the line of contact. Notable contributions by several research groups have enabled a broader understanding of the origin of capillary forces and have derived the analytical expressions of these forces, 109-112 which are outside the scope of the current review. Here, we will review some of the recent advances that have been made in capillary mediated assembly and their role in gelation and rheological processes.

The group of Whitesides was among the first to report the assembly via lateral capillary forces of millimeter and submicron scale objects into two dimensional arrays at the perfluorodecalin/water interface. 120,121 Capillary assembly of shape anisotropic colloids such as ellipsoids with different material properties has also been investigated. 34,113,122,123 At relatively small surface coverage, bare polystyrene ellipsoids at the water-oil interface have been observed to assemble tip-totip, while silica-coated polystyrene ellipsoids assembled side-toside (Fig. 4b). Surprisingly, as the solid fraction is increased, charged polystyrene ellipsoids change the assembly configuration at either the oil-water or air-water interface and form compact percolating networks with local dominance of triangular or flower-like structures. 123 By changing the particle shape from ellipsoids to cylinders, structurally different architectures such as end-to-end assemblies on planar interface at low particle concentration (Fig. 4c) or "bamboo like" structures at higher particle concentration have been observed. 114,122

Capillary bridging of patchy colloids also opens opportunities to form hierarchical structures. Solid patches are generally used, and liquid patches have been examined in a few recent studies. Zhao et al. showed a simple method of forming 1D colloidal chains by capillary bridging. 115 Polystyrene discs with two liquid patches were centrifuged, during which the liquid patch of the discs compressed against each other and formed bridges bind the discs in a directional chain with parallel orientation (Fig. 4d inset). The length of the chains increased with repeated cycles of centrifugation until they merged into long fibers without any external fields as exemplified in Fig. 4d.

Higher ordered structures can also be made using capillary bridging. Our group used polystyrene microbeads with iron oxide patch on one hemisphere selectively wetted with liquid lipid fatty acids that can aggregate into three-dimensional clusters by directed capillary bridging. 116 By using different sized particles, we were able to observe biparticle dimers, trimers (Fig. 4e top), hexamers and even particle rings. The cluster arrangement is guided by the balance between electrostatic repulsion and capillary bridging forces of the liquid phase of the fatty acids. Monte Carlo simulations showed how the assembly was affected by changing the patch areas. Further, by incorporating double patches on the particles, the arrangement hierarchy shifted from 3D to 2D clusters because of an additional directionality in the assembly that facilitated the formation of elongated structures (Fig. 4e bottom). Disassembly of colloidal structures is also an important aspect that has been studied recently in applications which require high surface-to-volume ratio. 116,124,125 Interestingly, in the case of capillary mediated assembly, temperature-driven switching of these fatty acids from fluid to gel phases or swelling/deswelling of the patches around the particles is possible. In suitable solvents, this provides a variable that can be used to reversibly control the assembly/disassembly of the clusters. 116,126 Finally, capillary bridging can be combined with polymerization to construct complex permanent clusters. 127,128

Capillary forces are efficient in the assembly of particles in that they can overcome repulsive electrostatic forces and are usually larger than van der Waals forces, giving rise to strong and cohesive colloidal structures. Even a small fraction of secondary liquid forming capillary bridges between particles could form percolated network in a concentrated multiphase suspension. 117,119,129,130 Capillary suspension can be formed with either the secondary fluid wetting the particles more favorably than the bulk phase, which is called the pendular state, or less favorably than the bulk, which is called the capillary state (Fig. 4f). In both cases, the capillary suspension can transition from a viscous fluid to a gel-like material due to a meniscus particle bridging. This can result in dramatic changes to the rheological properties of a suspension. 131-134 It has been shown that increase in the wetting liquid's volume fraction also results in states without percolated network formation, such as Pickering emulsions, Bijels or spherical agglomerates.

Capillary force offers strong yet controlled binding and aggregation in a liquid medium. Capillary force-mediated gelation has also been studied by Hoffman et al. to establish how particle size affects the rheology of suspensions and gels, as quantified by their yield stress and shear viscosity. 119,134 To quantify the capillary gel's strength versus particle size relationship, they prepared suspensions of hydrophilic glass microbeads with different sizes in liquid diisononyl phthalate (hydrophobic medium). While both samples immediately gelled due to strong capillary force interactions, the sample with larger glass beads formed a weak gel that sagged under its own weight (Fig. 4h), inferring that the mechanical strength of the gel is inversely proportional to the radius of the constituent particles. Particle surface roughness was also found to influence the rheology of capillary suspensions, as weaker and less clustered structures were formed when increasing particle roughness.135 Such ability to tune the material properties is specifically useful when making capillary pastes for applications

such as extrusion-based 3D printing. 136–138 The resulting structures can be made reconfigurable by modifying parameters such as temperature, wetting liquid properties, and the three-phase contact angle. Our group presented a simple universal technique for making "homocomposite" capillary pastes for 3D printing. 118 It uses the same common silicone base (polydimethylsiloxane, PDMS) for making elastomeric particles as well as the liquid capillary binder phase. We prepared dispersions of PDMS microbeads by emulsion polymerization. These beads were gelled by capillary bridging action after uncured PDMS liquid precursor is added to the suspension (Fig. 4g). The result is a capillary paste with yield stress that can be conveniently extruded by 3D printing as discussed in Section 7.

5. Assembly at fluid-fluid interfaces using magneto-capillary interactions

The synergistic combination of easy to control magnetic actuation and long-range reconfigurable capillary interactions allows to construct a variety of structures with remarkable properties and dynamic responses. Time-varying magnetic fields could be applied to form reconfigurable out-of-equilibrium particle patterns at interfaces. Millimeter size-discs deposited on the water surface can spin in place with an angular speed equal to that of the applied rotating magnetic field from the bottom. 139 Disc spinning was found to generate hydrodynamic forces which induced repulsive interactions, while the discs were simultaneously attracted towards the axis of the rotating field. This interplay between these competing forces led to the formation of dynamic assemblies with unusual ordering. An in-plane rotating magnetic field operating at a frequency of 1 Hz in conjunction with a vertical uniform magnetic field can lead to collection of metallic spheres suspended at the airwater surface rotating jointly at an angular speed of 0.3 rad s⁻¹ (Fig. 5a). 140 The rotational speed was found to be dependent on both frequency and strength of the field. The authors suggest that such non-reciprocal motion can be used for the design of microswimmers.

Magnetic colloidal dispersions can also assemble in unique patterns at fluid interfaces by applying an alternating magnetic field perpendicular to the air-water interface. A ferromagnetic dispersion can self-organize into "snake-like" structures illustrated in Fig. 5b. 37,141,142 Each segment of these structures consists of ferromagnetically aligned microparticles, while the segments are antiferromagnetically oriented to each other. Pure magnetic interactions would make this configuration energetically unfavorable. Therefore, the authors attributed this pattern formation to the collective effect of magnetic dipolar interactions and induced hydrodynamic flows. The particles form aligned chains due to dipole-dipole interactions, while simultaneously dragging the surrounding fluid by their local oscillations at the interface. This combination leads to the formation of snake-like dissipative structures. Replacing the liquid-air interface with liquid-liquid interface can modify the outcome

of such dynamic self-assembly and particles at an interface of two immiscible liquids exhibited the formation of localized asters (Fig. 5c).¹⁴³ This dynamic self-assembly pattern is promoted by the interplay between the interface's excitations and a collective response of the magnetic colloids to the external alternating field.¹⁴⁴ Upon application of a small static in-plane magnetic field one can open-up and navigate the motile asters.

Davies *et al.* have investigated the behavior of shapeanisotropic (ellipsoidal) particles adsorbed at fluid-fluid interfaces under the influence of a magnetic field. ¹⁴⁶ In absence of a magnetic field, the major axis of the ellipsoidal particles aligned along the interface without any surface deformation. When a magnetic field was applied normal to the interface, the magnetic torque tried to align the particles along the field. This caused menisci formation at the interfaces with depression on one side and elevation at the other and subsequent particle interactions. Monte Carlo simulation studies have also predicted similar discontinuous transitions and the critical field strength was found to be dependent on the particle size, aspect ratio and surface tension. ^{147,148} In a concentrated system, the ellipsoids assemble in "capillary caterpillars", and various configurations where particles align side-to-side (Fig. 5d). ³⁸

Xie et al. also investigated the interaction of Janus ellipsoidal particles adsorbed at fluid-fluid interface. 145 These particles are composed of polar and apolar halves of opposite wettability. By applying orthogonal uniaxial fields, the tilt angle of the Janus ellipsoids with respect to the interface can be tuned, which ultimately leads to the formation of various ordered structures such as clusters, chains, hexagonal lattices, and ring-like structures, as predicted from the simulation results (Fig. 5e). Similar simulation studies have been done by Xie et al. on the interface deformation by Janus particles adsorbed at fluid-fluid interfaces under the influence of a homogenous magnetic field. 149 Lattice-Boltzmann simulations predicted dipolar deformation of the interface, which increased linearly for smaller tilt angles and reached a constant value for higher tilt angles till 90°. Using this fundamental interpretation of dipolar capillary interactions of Janus particles at the interfaces, they further developed a pair-interaction model that predicted that these particles would arrange into a side-side configuration in a concentrated system and form monolayer structures. The particles arranged into long, straight chains, in contrast to the structures formed by capillary interactions between ellipsoidal particles. 150

Magneto-capillary forces in the bulk of liquid phases can also be used to form flexible particle chains and networks. One such example is the magnetic assembly of Fe₂O₃ nanoparticles surrounded by a surface-condensed liquid lipid layer. ^{39,151} Our group demonstrated that under the influence of a uniform magnetic field, the lipid-bound nanoparticles formed microfilaments, which have extremely high flexibility due to the lipid capillary bridges between the nanoparticles (Fig. 5f). The capillary bridges were able to reform and self-repair by reconnecting the broken filaments when the magnetic field was re-applied (Fig. 5g). The filaments were fully stretched under constant magnetic field and tried to follow the field direction. Once complex

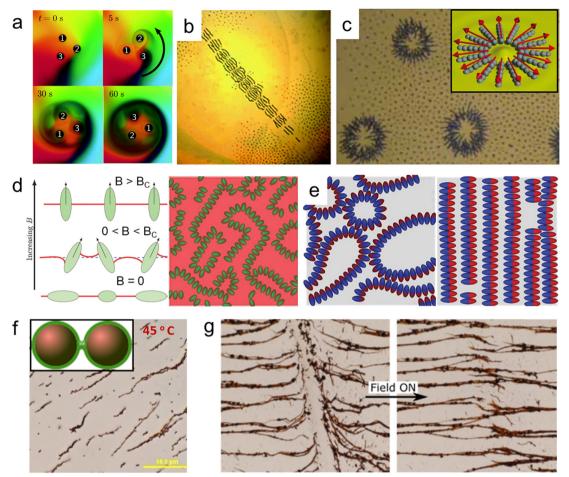


Fig. 5 Magneto-capillary assembly of colloidal particles: (a) locomotion of a capillary assembly of 500 μm magnetic spherical particles exposed to vertical and a horizontal rotating fields. Reproduced with permission from ref. 140. Copyright 2019, Royal Society of Chemistry. (b) Self-assembled "snake" like patterns with multiple segments generated by an AC magnetic field at an air—water interface. Reproduced with permission from ref. 37. Copyright 2006, American Physical Society (c) self-assembled dynamic asters at the liquid—liquid interface (left) and schematics of a magnetic ordering in asters (right). Reproduced with permission from ref. 36. Copyright 2011, Nature. (d) Schematic of the alignment of ellipsoidal magnetic particles with increasing field (left) and formation of "capillary caterpillars" of ellipsoidal particles in side-by-side configuration at air—liquid interface (right). Reproduced with permission from ref. 38. Copyright 2014, Wiley-VCH. (e) Magnetic assembly of ellipsoidal "Janus" particles into structures such as rings, chains, and hexagonal lattices. Reproduced with permission from ref. 145. Copyright 2021, Wiley-VCH. (f) Permanent flexible filaments magnetically assembled by Fe₂O₃ nanoparticles bound by liquid fatty acid. The inset shows the schematic of liquid nanocapillary bridging between the nanoparticles. Reproduced with permission from ref. 39. Copyright 2015, Nature. (g) Self-repairing capability of the microfilaments where the broken filaments reconnect with each other after applying magnetic field. Reproduced with permission from ref. 39. Copyright 2015, Nature.

fields such as rotating magnetic ones were introduced, the filaments curled, stretched, bent, and bundled, giving rise to a variety of unusual shapes such as closed rings, or closed infinity signs. Similar principles for capillary binding of magnetically responsive structures were used in the formation of 3D printable pastes described in Section 7.

6. Magnetically responsive foams, gels, and coatings

Various combinations of magnetic and capillary forces can be encountered in many classes of multiphasic systems of practical importance, including foams, emulsions, gels, and coatings. We review below recent advances in such areas leading to novel responsive and reconfigurable systems.

Foams

Pickering stabilization of foams by adding solid particles to the dispersion has been established for long; but only relatively recently researchers have shown how the Pickering foam stability can be manipulated using external fields. One simple way to make field-responsive foams is the introduction of the inorganic magnetically responsive particles to foams which can stabilize the foams and allow their manipulation by an external magnetic field. Similarly, Pickering emulsions containing paramagnetic particles can be reversibly switched between biphasic dispersions and fully phase-separated fluids upon application of a magnetic field. Magnetically responsive particles can also be used to tune the shape and stabilities of the bubbles in the foams using an external magnetic field. Soetanto and Watarai showed the motion control

of 10 µm sized bubbles stabilized by submicron magnetite particles. The magnetic particles functioned as both the force mediator and the bubble stabilizer. Magnetic fields can be used to twist the structures and tune the size of the bubbles in ferrofluid foams¹⁶¹ and other magnetically responsive foams stabilized by hydrophobic magnetic nanoparticles. 156

The introduction of magnetic particles in Pickering foams also enables the formation of foam systems with on-demand breakdown and release as reported by Lam et al. 165 The foams containing hypromellose phthalate particles, with embedded

carbonyl iron particles were stable for more than a week in the absence of magnetic fields but readily destabilized within seconds when a magnetic field above a certain strength was applied (Fig. 6a). The breakdown of fresh foams was slow as the higher water content allowed for the migration of individual particles towards the field gradient, followed by the ejection of the air bubbles. 162 The liquid drainage from the films between the bubbles with aging led to thin, but fragile, films. These films are instantly broken by the magnetic particles when a field is applied, resulting in instantaneous foam collapse.

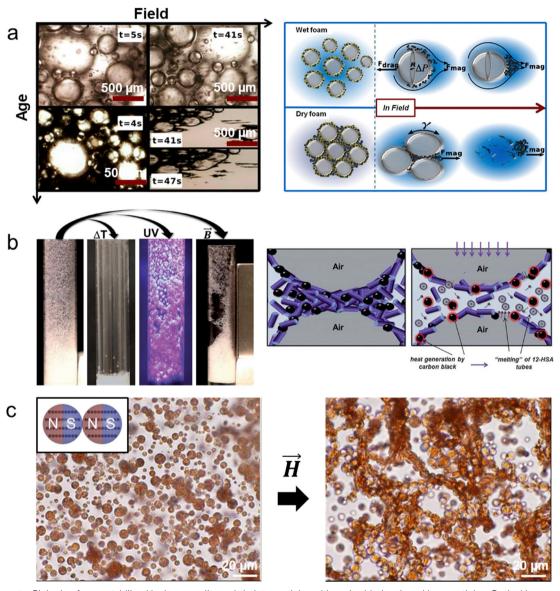


Fig. 6 (a) Magneto-Pickering foams stabilized by hypromellose phthalate particles with embedded carbonyl iron particles. Optical images of collapse of wet foam (top) and dry foam (bottom) and a schematic of their corresponding destabilization mechanisms in magnetic fields. Wet foam collapses due to ejection of bubbles from the foam matrix, while the dry foam collapse occurs due to film breakup and bubble coalescence. Reproduced with permission from ref. 162. Copyright 2013, American Chemical Society. (b) Foams prepared using 12-hydroxystearic acid containing magnetic particles destabilized by multiple stimuli including increase in temperature, UV irradiation and magnetic field exposure (left). Schematic illustrating the collapse of the foam after UV irradiation (right). Reproduced with permission from ref. 163. Copyright 2013, Royal Society of Chemistry. (c) Magneto-responsive gels derived using soft elastomeric PDMS microbeads with embedded chains of iron-oxide nanoparticles. After switching on the field, the dispersed beads aligned themselves along the field direction and formed percolated network-like structures. Reproduced with permission from ref. 164. Copyright 2021, American Chemical Society

Manipulation of Pickering emulsion can also be achieved by heating up the metal particles present in the foam matrix as shown by Kaiser et al. 166 Magnetic heating in the presence of an alternating field, can lead to complete miscibility of all components of the emulsion, which collapses the emulsion.

The next goal in this research area was to synthesize multifield responsive soft materials based on foams. Fameau et al. reported the first multi-responsive foams with thermo-photomagneto-controlled stability. 163 These foams were prepared by stabilizing the foams with carbon black particles (CBP) or and a thermo-responsive fatty acid, 12-hydroxystearic acid (12-HSA). 162,167 In the absence of UV irradiation, the 12-HAS forms tubular micelles, which jammed to form gel-like layers inside the foam films and trapped the CBP particles. CBP particles are intense light absorbers that in turn result in a rise in temperature, when exposed to UV light. The molecular 12-HAS assemblies transformed to micelles, thereby destabilizing the foam (Fig. 6b). Thus, Fameau et al. were able to rapidly defoam systems also containing magnetic carbonyl iron particles by either light, heat or by applying an external magnetic field.

Gels

Magnetorheological gels (MRG) have also been a topic of investigations due to their potential applications in sensors, magnetoresistors, vibration control, brakes, mechanical dampers, and electromechanical devices. 168-171 Structurally, MRGs can be considered as an intermediate of magnetorheological fluids (MRFs) and magnetorheological elastomers (MREs). Gels are more liquid-like than the solid elastomers and allow for magnetic particle reconfiguration. Castellanos et al. reported magnetic-field induced gels composed of PDMS beads with embedded magnetically assembled and aligned chains of Fe₂O₃ nanoparticles (Fig. 6c). 164 The formation of a percolated network between the microbeads made the system switch from fluid-like to gel-like structure upon turning on the field. These networks could be broken and reformed by cyclic demagnetization and remagnetization. Furthermore, as mentioned in the previous section, the combination of the magnetic and capillary interactions allows the formation of magnetically responsive capillary gels.³⁹ The dynamic response of such magnetic gels can be tuned by varying system parameters such as introducing an external field, varying the spatial magnetic particle distribution inside the polymer matrix, or the orientation memory of the particles. 172 Their magnetoresistance and elastic modulus could be further conveniently and reversibly adjusted by using magnetic fields. 170,173

Lalitha et al. presented the design and synthesis of magnetically responsive self-healing gels composed of renewable resources. 171 They incorporated Fe₃O₄ nanoparticles into the gel matrix by sonication and demonstrated successful selfrepair of these gels both in air and water medium. Other examples of biodegradable magnetic polymer gels are presented by Chatterjee et al., who used hydroxy-propyl cellulose and surfactant-modified maghemtie to synthesize a nanomagnetic gel using an emulsion method. 174,175 Akin to the multi-stimuli responsive foams, researchers have also aimed

to investigate multiresponsive colloidal gels. For example, Braim et al. reported thermoresponsive magnetic colloidal gels composed of PDEGMA/poly(chloromethlystyrene) microspheres and Fe₃O₄ magnetic nanoparticles, which showed good cytocompatibility and could be used as 3D scaffolds for in vitro stimulation of cells. 176 Other types of thermoresponsive magnetic hydrogels and their applications are discussed in numerous reports. 1777-179 Thus, both magnetic foams and gels are finding use in variety of fundamental studies and industrial applications.

One emerging application of comprehensive gel-based systems is in "slime robots," which represent a new class of magnetic robots based on liquid metal or ferrofluid. 180-183 Because of their fluid or gel-like characteristics, they exhibit better deformability than elastomer-based soft robots and can be guided to move and to pass through restricted spaces such as biological tissues. Sun et al. demonstrated one such fluid-based microrobot actuated by magnetic field, which can serve in various functions such as transportation, grasping objects, human motion monitoring, and circuit switching and repair. 181

Coatings

Lee et al. presented a method of making coatings by utilizing the magnetic response of ferrofluid containing nonmagnetic colloidal particles. 184 Drying of droplets to deposit coatings from colloidal suspension leads to migration of the particles towards the edge of the droplets due to convective assembly, thereby forming coffee rings. The researchers showed how the coffee ring effect can be overcome by applying magnetic fields to a mixture of Fe₃O₄ nanoparticles and polystyrene latex beads. The direction of the particle motion towards the drying periphery was reversed as the field was switched on, causing them to move back from the edge and towards the center. This led to the formation of a particle-rich state at the center, with disc-like structures. This magnetostatic microconvection technique can be used in the deposition of functional coatings.

7. Responsive soft composites via magnetic and capillary interactions

The making of soft structures that can be reconfigured by external stimuli often requires the formation of lattices and networks of complex shape. 3D printing has emerged as an advanced fabrication tool for making soft reconfigurable structures due to its rapid prototyping capability. One of the most common methods for 3D printing of soft matter is direct ink writing (DIW) commonly based on extrusion of filaments through a nozzle. The gentle processing allows the extrusion of soft matter such as hydrogels 185,186 or elastomers. 187,188 The soft inks used for extrusion often contain particles or rheology modifiers to adjust yield stress and shear thinning, which allows extrusion at high shear stress followed by rapid solidification. De facto, the pastes used in 3D printing by extrusion are commonly a soft composite material on their own.

Common rheology modifiers that have been used to impart viscoelastic properties in extrudable pastes include fumed silica and clay particles. In addition to having the right rheological characteristics, the internal or external structure of extruded filaments can be engineered to include components that encode shape reconfiguration for applications such as soft actuators, 188-191 novel responsive gels, 28,163,192,193 biomedical applications, 194,195 and new drug delivery techniques. 196,197 One such example is biomimetic 4D (time-dependent) printing of hydrogel inks (Fig. 7a). 186 Cellulose fibrils could be used for internal structuring of the gels, where, after being shear-aligned during the ink extrusion, they can gave rise to their anisotropic swelling/deswelling and shape reconfiguration. 193,198-200

Due to the rapid shape reconfiguration and untethered manipulation, magnetic field-directed 3D printed structures are a suitable core of soft actuators and soft robotics. The mechanical response of these structures can be programmed by the 3D printed structure and modulated by the remotely applied fields. Our group used the homocomposite capillary inks mentioned earlier as a basis of 3D printed soft magnetocapillary actuators. 118,188 We embedded carbonyl iron particles

into the silicone microbeads by adding the particles to the silicone droplets before curing (Fig. 7b left). The cured composite microbeads were bound by liquid silicone into capillary paste. The final 3D-printed and crosslinked silicone meshes are hydrophobic and thus can be suspended on the surface of water while supported by interfacial tension. These floating meshes can be actuated by the joint action of magnetic field and lateral capillary interactions. 3D printed structures were floated at the interface between air and water held in Petri dish. When magnetic field (with an attractive gradient) was applied from below the dish, the floating mesh was pulled down, while the increasing lateral capillary attraction led to mesh re-configuration and compression. The compression patterns were determined by spatial design of the meshes. The reconfiguration outcomes depended on the mesh patterns, including auxetic type lattices and droplet microdispensers (Fig. 7b right). Another example of 3D printed homocomposite hydrogel made in our lab, where both the primary matrix and the reinforcement networks are made of sodium alginate, is shown in Fig. 7c. 201 The hydrogels are reinforced by a second colloidal networks made of fibrillar branched alginate soft dendritic colloids. The printed

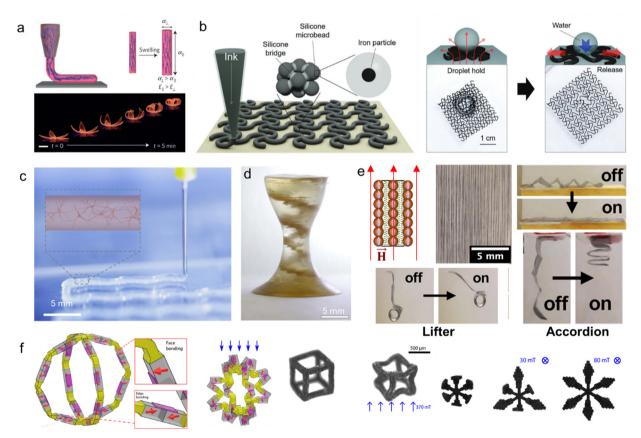


Fig. 7 (a) Example of biomimetic 4D printing and the folding of the structures upon swelling. Reproduced with permission from ref. 186. Copyright 2016, Nature Publishing Group. (b) 3D printing of homocomposite magnetic ink made of silicone and mesh actuation on water surface by magnetic field. Reproduced with permission from ref. 188. Copyright 2019, Wiley-VCH. (c) 3D printing of sodium alginate homocomposite ink. The molecular alginate hydrogel is reinforced with soft dendritic colloids also made of alginate. Reproduced with permission from ref. 201. (d) Magnetic field-assisted 3D printing. Reproduced with permission from ref. 202. (e) Composite soft actuators made by embedding in elastomeric matrix pre-assembled chains of iron microparticles. Reproduced with permission from ref. 203. Copyright 2017, American Physical Society. (f) 3D miniature magnetic soft structures by heterogenous assembly using voxels of different magnetic moments. Reproduced with permission from ref. 204. Copyright 2021, AAAS.

colloidal-molecular network hydrogel shows better mechanical characteristics (storage modulus, Young's modulus) than either constitutive networks at the same concentration.

Kokkinis et al. reported how the 3D printing of composite materials can be enhanced by magnetic field (Fig. 7d).²⁰² They incorporated alumina platelets as texturable particles into polyurethane acrylate based ink. After ink ejection, the orientation of the platelets was guided by the application of an external magnetic field, giving rise to internal microstructural features. Kim et al. demonstrated in situ magnetic field-assisted 3D printing of magnetic actuators. 190 Ferromagnetic microparticles embedded in a silicone ink were polarized during extrusion; thus, the magnetic polarization pattern was embedded in the filament domains, which in turn enables programmable shape reconfiguration. Further, it has been shown that applying a magnetic field during extrusion-based 3D printing can control the rheology of the ink containing magnetic nanoparticles by increasing the microstructural strength of the final structures.²⁰⁵ This is a result of the field-induced interactions between the solid particles leading to chain or cluster formation. The viscosity of MR fluids generally increases with applied magnetic field, therefore incorporating MR fluids in the elastomer matrix during 3D printing can also alter the mechanical properties of the printed structures.

Magnetically responsive smart composite materials can also be synthesized by assembling magnetic nanoparticles and microparticles from suspension under applied fields into various configurations as discussed in Sections 2 and 3, and then incorporating these assemblies into a soft polymer matrix by solvent casting and bulk polymerization. The organized magnetic particles embedded into soft matrix yield magnetoactive elastomers (MAE). 203,204,206 The soft matrix can be made of thermoplastic polyurethane, 207 PDMS, 118 PNIPAM 208, 209 or even agarose hydrogel. Such MAE composites are subject to strong torque and bending in magnetic fields as the embedded chains try to align with the direction of the applied field. Thus, one can fabricate permanent materials which can be macroscopically guided depending on the particle structure assembled within the composites. 210-213 For example, Shmauch et al. used solvent casting method to embed magnetic field-aligned microparticles in an elastomer film. The resulting composite film was strongly and directionally responsive to an externally applied magnetic field. 203,207 This programmed response to an external magnetic field was used to demonstrate soft robotic actuation in applications such as valves, "arms" that can lift up to 50× the matrix weight, and accordion folds that can stretch and contact (Fig. 7e).

Recent advances in the design and assembly of complex magnetically actuatable structures also involve the making and assembly of soft microscale units also known as "voxels," as building blocks of the soft machines. For example, Zhang et al. introduced a bottom-up assembly approach to fabricate smallscale 3D soft-bodied machines with high spatial resolution, which respond to magnetic fields. Their fabrication is based on a 3D heterogeneous integration approach with printed elastomeric voxels (Fig. 7f). 204,214 These authors demonstrate complex shapes with directional magnetic response and reconfiguration. Such comprehensive structures made of predesigned units have promise for numerous applications in future biomedical practice.

Summary and outlook

This perspective illustrates the extremely rich variety of flexible and responsive colloidal structures that encompass variations of magnetic and capillary interactions. Both of these interactions represent valuable tools in the "interaction toolbox" that can be used to assemble and manipulate reconfigurable soft matter. This is a result of a few characteristics that are common for both magnetic and capillary interactions: (1) they are extremely long ranged and "soft" on the colloidal scale. Unlike the omnipresent electrostatic and van der Waals interactions which operate on distances up to tens of nanometers, the magnetic and capillary interactions could extend to distances of hundreds of microns or even millimeters. Their decay with distance, d, is commonly expressed as proportional to d^{-2} . (2) The capillary attraction is also unique in that it does not lead to irreversible adhesion of the particles and allows their reconfiguration even when strongly held together by the capillary menisci. (3) They could either be unidirectional or strongly oriented. The dipolar and gradient driven magnetic attraction are strongly dependent on the particle orientation and position, while many capillary interactions can be strongly specific. However, both interactions can operate on particles in unform fields or at sloped menisci. (4) They could be reversible or reconfigurable. The interactions can be easily turned on and off on demand, by turning on the magnetic field, or adding more liquid, or surfactants, for the case of capillary forces. (5) Last, but not least, they are simple to implement. The magnetic fields can be applied efficiently and reliably across many colloidal and biomedical targets using sets of electronically switched electromagnets. The field magnitude and gradient directions are easily controlled and modelled.

These convenient, controllable, and predictable interactions have found many applications, exemplified in this paper. The rich variety of structures reviewed here by no means exhaust all the possible applications or physical effects enabled by capillarity and magnetic field actuation in the formation and manipulation of soft matter systems. For example, one can add the element of active motility in such systems, making the particles travel along pre-designed trajectories before assembly by using the Marangoni effect of interfacial propulsion driven by release of surface-active species. 215,216 Given the continuing interest and expanding scope of investigation of reconfigurable, actuatable, and "active" soft matter, one can expect that the use of the capillary and magnetic interactions as simple and efficient means of making flexible and responsive assemblies will continue to enable exciting new scientific advances.

Conflicts of interest

There are no conflicts of interest to declare.

Acknowledgements

This paper is gratefully dedicated to the memory of Prof. Peter Kralchevsky, an outstanding scientist, who made seminal contributions to the theories of capillary forces and colloidal interactions. The authors acknowledge support from NSF grants CBET-1935248, CBET-2133983 and partially CMMI-1825476.

References

- 1 J. N. Israelachvili, D. J. Mitchell and B. W. Ninham, *Biochim. Biophys. Acta, Biomembr.*, 1977, **470**, 185–201, DOI: **10.1016/0005-2736(77)90099-2**.
- 2 X. Cui, S. Mao, M. Liu, H. Yuan and Y. Du, *Langmuir*, 2008, 24, 10771–10775, DOI: 10.1021/la801705y.
- 3 B. Gold, *Mol. Diagn. (2nd Ed.)*, 2009, 501–511, DOI: **10.1016**/B978-0-12-374537-8.00034-1.
- 4 J. Hernández-Rojas, D. Chakrabarti and D. J. Wales, *Phys. Chem. Chem. Phys.*, 2016, **18**, 26579–26585, DOI: **10.1039**/c6cp03085h.
- 5 S. C. Glotzer, M. J. Solomon and N. A. Kotov, *AIChE J.*, 2004, 50, 2978–2985, DOI: 10.1002/aic.10413.
- 6 A. M. Kalsin, M. Fialkowski, M. Paszewski, S. K. Smoukov, K. J. M. Bishop and B. A. Grzybowski, *Science*, 2006, 312, 420–424, DOI: 10.1126/science.1125124.
- 7 B. G. Prevo, D. M. Kuncicky and O. D. Velev, *Colloids Surf.*, A, 2007, 311, 2–10, DOI: 10.1016/j.colsurfa.2007.08.030.
- 8 O. D. Velev, N. D. Denkov, P. A. Kralchevsky, I. B. Ivanov, H. Yoshimura and K. Nagayama, *Prog. Colloid Polym. Sci.*, 1993, 93, 366–367, DOI: 10.1007/bfb0118623.
- B. Bharti and O. D. Velev, *Langmuir*, 2015, 31, 7897–7908,
 DOI: 10.1021/la504793y.
- 10 S. K. Smoukov, S. Gangwal, M. Marquez and O. D. Velev, Soft Matter, 2009, 5, 1285–1292, DOI: 10.1039/b814304h.
- 11 K. Han, C. W. Shields, N. M. Diwakar, B. Bharti, G. P. López and O. D. Velev, *Sci. Adv.*, 2017, 3, 1–7, DOI: 10.1126/ sciadv.1701108.
- 12 K. Han, C. W. Shields and O. D. Velev, Adv. Funct. Mater., 2018, 28, 1705953, DOI: 10.1002/adfm.201705953.
- 13 A. Al Harraq, J. G. Lee and B. Bharti, *Sci. Adv.*, 2020, **6**, 5337–5345, DOI: **10.1126/sciadv.aba5337**.
- 14 S. Gangwal, O. J. Cayre and O. D. Velev, *Langmuir*, 2008, **24**, 13312–13320, DOI: **10.1021/la8015222**.
- 15 J. P. Singh, P. P. Lele, F. Nettesheim, N. J. Wagner and E. M. Furst, *Phys. Rev. E: Stat., Nonlinear, Soft Matter Phys.*, 2009, 79, 050401, DOI: 10.1103/PhysRevE.79.050401.
- 16 D. Nagao, M. Sugimoto, A. Okada, H. Ishii, M. Konno, A. Imhof and A. Van Blaaderen, *Langmuir*, 2012, 28, 6546–6550, DOI: 10.1021/la204493m.
- 17 R. S. Hendley, L. Zhang and M. A. Bevan, Soft Matter, 2022, 18, 9273–9282, DOI: 10.1039/D2SM01078J.
- 18 X. Chen, L. Lin, Z. Li and H. B. Sun, *Adv. Funct. Mater.*, 2022, 32, 2104649, DOI: 10.1002/adfm.202104649.
- J. Zhang, J. Guo, F. Mou and J. Guan, *Micromachines*, 2018,
 88, DOI: 10.3390/mi9020088.

- 20 S. J. Boehm, L. Lin, K. Guzmán Betancourt, R. Emery, J. S. Mayer, T. S. Mayer and C. D. Keating, *Langmuir*, 2015, 31, 5779–5786, DOI: 10.1021/acs.langmuir.5b01633.
- 21 O. D. Velev and K. H. Bhatt, Soft Matter, 2006, 2, 738–750, DOI: 10.1039/b605052b.
- 22 M. Grzelczak, J. Vermant, E. M. Furst and L. M. Liz-Marzán, ACS Nano, 2010, 4, 3591–3605, DOI: 10.1021/nn100869j.
- 23 V. Liljeström, C. Chen, P. Dommersnes, J. O. Fossum and A. H. Gröschel, *Curr. Opin. Colloid Interface Sci.*, 2019, **40**, 25–41, DOI: **10.1016/j.cocis.2018.10.008**.
- 24 Z. Li, F. Yang and Y. Yin, Adv. Funct. Mater., 2020, 30, 1903467, DOI: 10.1002/adfm.201903467.
- 25 Z. Nie, D. Fava, E. Kumacheva, S. Zou, G. C. Walker and M. Rubinstein, *Nat. Mater.*, 2007, 6, 609–614, DOI: 10.1038/ nmat1954.
- 26 Q. Chen, J. Yan, J. Zhang, S. C. Bae and S. Granick, Langmuir, 2012, 28, 13555–13561, DOI: 10.1021/la302226w.
- 27 S. C. Glotzer and M. J. Solomon, *Nat. Mater.*, 2007, 6, 557–562, DOI: 10.1038/nmat1949.
- 28 S. R. Mishra, M. D. Dickey, O. D. Velev and J. B. Tracy, *Nanoscale*, 2016, 8, 1309–1313, DOI: 10.1039/c5nr07410j.
- 29 M. Wang, L. He and Y. Yin, *Mater. Today*, 2013, 16, 110–116, DOI: 10.1016/j.mattod.2013.04.008.
- 30 R. M. Erb, H. S. Son, B. Samanta, V. M. Rotello and B. B. Yellen, *Nature*, 2009, 457, 999–1002, DOI: 10.1038/ nature07766.
- 31 J. Yan, S. C. Bae and S. Granick, *Adv. Mater.*, 2015, 27, 874–879, DOI: 10.1002/adma.201403857.
- 32 N. Osterman, I. Poberaj, J. Dobnikar, D. Frenkel, P. Ziherl and D. Babić, *Phys. Rev. Lett.*, 2009, **103**, 228301, DOI: **10.1103/PhysRevLett.103.228301**.
- 33 I. B. Liu, N. Sharifi-Mood and K. J. Stebe, Annu. Rev. Condens. Matter Phys., 2018, 9, 283–305, DOI: 10.1146/ annurev-conmatphys-031016-025514.
- 34 L. Botto, E. P. Lewandowski, M. Cavallaro and K. J. Stebe, Soft Matter, 2012, 8, 9957–9971, DOI: 10.1039/c2sm25929j.
- 35 S. Ni, L. Isa and H. Wolf, *Soft Matter*, 2018, **14**, 2978–2995, DOI: **10.1039/c7sm02496g**.
- 36 A. Snezhko and I. S. Aranson, *Nat. Mater.*, 2011, **10**, 698-703, DOI: **10.1038/nmat3083**.
- 37 A. Snezhko, I. S. Aranson and W. K. Kwok, *Phys. Rev. Lett.*, 2006, **96**, 078701, DOI: **10.1103/PhysRevLett.96.078701**.
- 38 G. B. Davies, T. Krüger, P. V. Coveney, J. Harting and F. Bresme, Adv. Mater., 2014, 26, 6715–6719, DOI: 10.1002/ adma.201402419.
- 39 B. Bharti, A. L. Fameau, M. Rubinstein and O. D. Velev, Nat. Mater., 2015, 14, 1104–1109, DOI: 10.1038/nmat4364.
- 40 P. Moritz, A. Gonon, T. Blon, N. Ratel-Ramond, F. Mathieu, P. Farger, J. M. Asensio-Revert, S. Cayez, D. Bourrier, D. Saya, L. Nicu, G. Viau, T. Leïchlé and L. M. Lacroix, ACS Nano, 2021, 15, 5096–5108, DOI: 10.1021/acsnano.0c10215.
- 41 J. Faraudo, J. S. Andreu and J. Camacho, *Soft Matter*, 2013, **9**, 6654–6664, DOI: **10.1039/c3sm00132f**.
- 42 J. H. E. Promislow, A. P. Gast and M. Fermigier, *J. Chem. Phys.*, 1995, **102**, 5492–5498, DOI: **10.1063/1.469278**.

Soft Matter

- 43 C. P. Reynolds, K. E. Klop, F. A. Lavergne, S. M. Morrow, D. G. A. L. Aarts and R. P. A. Dullens, J. Chem. Phys., 2015, 143, 214903, DOI: 10.1063/1.4936323.
- 44 J. Ge, H. Lee, L. He, J. Kim, Z. Lu, H. Kim, J. Goebl, S. Kwon and Y. Yin, J. Am. Chem. Soc., 2009, 131, 15687-15694, DOI: 10.1021/ja903626h.
- 45 Y. Hu, L. He and Y. Yin, Angew. Chem., Int. Ed., 2011, 50, 3747-3750, DOI: 10.1002/anie.201100290.
- 46 L. He, M. Wang, J. Ge and Y. Yin, Acc. Chem. Res., 2012, 45, 1431-1440, DOI: 10.1021/ar200276t.
- 47 S. L. Biswal and A. P. Gast, Phys. Rev. E: Stat., Nonlinear, Soft Matter Phys., 2004, 69, 9, DOI: 10.1103/PhysRevE.69.041406.
- 48 E. M. Furst, C. Suzuki, M. Fermigier and A. P. Gast, Langmuir, 1998, 14, 7334-7336, DOI: 10.1021/la980703i.
- 49 J. Byrom, P. Han, M. Savory and S. L. Biswal, Langmuir, 2014, 30, 9045-9052, DOI: 10.1021/la5009939.
- 50 M. Fermigier and A. P. Gast, J. Colloid Interface Sci., 1992, 154, 522-539, DOI: 10.1016/0021-9797(92)90165-I.
- 51 E. M. Furst and A. P. Gast, Phys. Rev. E: Stat. Phys., Plasmas, Fluids, Relat. Interdiscip. Top., 2000, 62, 6916-6925, DOI: 10.1103/PhysRevE.62.6916.
- 52 J. M. Laskar, J. Philip and B. Raj, Phys. Rev. E: Stat., Nonlinear, Soft Matter Phys., 2009, 80, 041401, DOI: 10.1103/PhysRevE.80.041401.
- 53 Y. Nagaoka, H. Morimoto and T. Maekawa, Langmuir, 2011, 27, 9160-9164, DOI: 10.1021/la201156q.
- 54 J. H. E. Promislow and A. P. Gast, Langmuir, 1996, 12, 4095-4102, DOI: 10.1021/la960104g.
- 55 J. W. Swan, J. L. Bauer, Y. Liu and E. M. Furst, Soft Matter, 2014, 10, 1102-1109, DOI: 10.1039/c3sm52663a.
- 56 N. Osterman, D. Babič, I. Poberaj, J. Dobnikar and P. Ziherl, Phys. Rev. Lett., 2007, 99, 248301, DOI: 10.1103/ PhysRevLett.99.248301.
- 57 P. J. Camp, Phys. Rev. E: Stat., Nonlinear, Soft Matter Phys., 2003, 68, 061506, DOI: 10.1103/PhysRevE.68.061506.
- 58 G. Malescio and G. Pellicane, Nat. Mater., 2003, 2, 97-100, DOI: 10.1038/nmat820.
- 59 A. K. Vuppu, A. A. Garcia and M. A. Hayes, Langmuir, 2003, 19, 8646-8653, DOI: 10.1021/la034195a.
- 60 S. Melle, G. G. Fuller and M. A. Rubio, Phys. Rev. E: Stat. Phys., Plasmas, Fluids, Relat. Interdiscip. Top., 2000, 61, 4111-4117, DOI: 10.1103/PhysRevE.61.4111.
- 61 D. H. De Jong, G. Singh, W. F. D. Bennett, C. Arnarez, T. A. Wassenaar, L. V. Schäfer, X. Periole, D. P. Tieleman and S. J. Marrink, J. Chem. Theory Comput., 2013, 9, 687-697, DOI: 10.1021/ct300646g.
- 62 J. E. Martin, R. A. Anderson and C. P. Tigges, J. Chem. Phys., 1999, 110, 4854-4866, DOI: 10.1063/1.478389.
- 63 J. E. Martin, R. A. Anderson and C. P. Tigges, J. Chem. Phys., 1998, 108, 7887-7900, DOI: 10.1063/1.476226.
- 64 T. G. Kang, M. A. Hulsen, P. D. Anderson, J. M. J. Den Toonder and H. E. H. Meijer, Phys. Rev. E: Stat., Nonlinear, Soft Matter Phys., 2007, 76, 066303, DOI: 10.1103/ PhysRevE.76.066303.
- 65 I. Petousis, E. Homburg, R. Derks and A. Dietzel, Lab Chip, 2007, 7, 1746-1751, DOI: 10.1039/b713735b.

- 66 T. Yang, B. Sprinkle, Y. Guo, J. Qian, D. Hua, A. Donev, D. W. M. Marr and N. Wu, Proc. Natl. Acad. Sci. U. S. A., 2020, 117, 18186-18193, DOI: 10.1073/pnas.2007255117.
- 67 P. Vázquez-Montejo, J. M. Dempster and M. O. De La Cruz, Phys. Rev. Mater., 2017, 1, 064402, DOI: 10.1103/PhysRev Materials.1.064402.
- 68 K. Zahn, R. Lenke and G. Maret, Phys. Rev. Lett., 1999, 82, 2721-2724, DOI: 10.1103/PhysRevLett.82.2721.
- 69 E. Hilou, D. Du, S. Kuei and S. L. Biswal, Phys. Rev. Mater., 2018, 2, 025602, DOI: 10.1103/PhysRevMaterials.2.025602.
- 70 E. Hilou, K. Joshi and S. L. Biswal, Soft Matter, 2020, 16, 8799-8805, DOI: 10.1039/d0sm01100b.
- 71 E. Yammine, E. Souaid, S. Youssef, M. Abboud, S. Mornet, M. Nakhl and E. Duguet, Part. Part. Syst. Charact., 2020, 37, 1-12, DOI: 10.1002/ppsc.202000111.
- 72 S. Ravaine and E. Duguet, Curr. Opin. Colloid Interface Sci., 2017, 30, 45-53, DOI: 10.1016/j.cocis.2017.05.002.
- 73 W. Li, H. Palis, R. Mérindol, J. Majimel, S. Ravaine and E. Duguet, Chem. Soc. Rev., 2020, 49, 1955-1976, DOI: 10.1039/c9cs00804g.
- 74 A. B. Pawar and I. Kretzschmar, Macromol. Rapid Commun., 2010, 31, 150-168, DOI: 10.1002/marc.200900614.
- 75 A. K. Pearce, T. R. Wilks, M. C. Arno and R. K. O'Reilly, Nat. Rev. Chem., 2021, 5, 21-45, DOI: 10.1038/s41570-020-00232-7.
- 76 D. Lisjak and A. Mertelj, Prog. Mater. Sci., 2018, 95, 286-328, DOI: 10.1016/j.pmatsci.2018.03.003.
- 77 J. A. Champion, Y. K. Katare and S. Mitragotri, Proc. Natl. Acad. Sci. U. S. A., 2007, 104, 11901-11904, DOI: 10.1073/ pnas.0705326104.
- 78 Z. Wang, Z. Wang, J. Li, S. T. H. Cheung, C. Tian, S. H. Kim, G. R. Yi, E. Ducrot and Y. Wang, J. Am. Chem. Soc., 2019, 141, 14853-14863, DOI: 10.1021/jacs.9b07785.
- 79 C. Wyatt Shields Iv, S. Zhu, Y. Yang, B. Bharti, J. Liu, B. B. Yellen, O. D. Velev and G. P. López, Soft Matter, 2013, 9, 9219-9229, DOI: 10.1039/c3sm51119g.
- 80 M. N. Popescu, Langmuir, 2020, 36, 6861-6870, DOI: 10.1021/acs.langmuir.9b03973.
- 81 J. Hu, S. Zhou, Y. Sun, X. Fang and L. Wu, Chem. Soc. Rev., 2012, 41, 4356-4378, DOI: 10.1039/c2cs35032g.
- 82 E. Poggi and J. F. Gohy, Colloid Polym. Sci., 2017, 295, 2083-2108, DOI: 10.1007/s00396-017-4192-8.
- 83 A. Walther and A. H. E. Müller, Chem. Rev., 2013, 113, 5194-5261, DOI: 10.1021/cr300089t.
- 84 G. Loget and A. Kuhn, J. Mater. Chem., 2012, 22, 15457-15474, DOI: 10.1039/c2jm31740k.
- 85 E. Yammine, E. Souaid, S. Youssef, M. Abboud, S. Mornet, M. Nakhl and E. Duguet, Part. Part. Syst. Charact., 2020, 37, 2000111, DOI: 10.1002/ppsc.202000111.
- 86 B. Ren, A. Ruditskiy, J. H. Song and I. Kretzschmar, Langmuir, 2012, 28, 1149-1156, DOI: 10.1021/la203969f.
- 87 J. Yan, S. C. Bae and S. Granick, Adv. Mater., 2015, 27, 874-879, DOI: 10.1002/adma.201403857.
- 88 J. Yan, M. Bloom, S. C. Bae, E. Luijten and S. Granick, Nature, 2012, 491, 578-581, DOI: 10.1038/nature11619.
- 89 K. P. Herlihy, J. Nunes and J. M. DeSimone, Langmuir, 2008, 24, 8421-8426, DOI: 10.1021/la801250g.

- 90 J. P. Rolland, B. W. Maynor, L. E. Euliss, A. E. Exner, G. M. Denison and J. M. DeSimone, *J. Am. Chem. Soc.*, 2005, 127, 10096–10100, DOI: 10.1021/ja051977c.
- 91 C. W. Shields, Y.-K. Kim, K. Han, A. C. Murphy, A. J. Scott, N. L. Abbott and O. D. Velev, *Adv. Intell. Syst.*, 2020, 2, 1900114, DOI: 10.1002/aisy.201900114.
- 92 K. Han, C. W. Shields, B. Bharti, P. E. Arratia and O. D. Velev, *Langmuir*, 2020, **36**, 7148–7154, DOI: **10.1021**/ **acs.langmuir.9b03698**.
- 93 J. Yan, K. Chaudhary, S. Chul Bae, J. A. Lewis and S. Granick, Nat. Commun., 2013, 4, 1–9, DOI: 10.1038/ncomms2520.
- 94 E. Guzmán, F. Ortega and R. G. Rubio, *Langmuir*, 2022, 38, 13313–13321, DOI: 10.1021/acs.langmuir.2c02038.
- 95 H. J. Butt, *Langmuir*, 2008, **24**, 4715–4721, DOI: **10.1021**/la703640f.
- 96 L. Yao, L. Botto, M. Cavallaro, B. J. Bleier, V. Garbin and K. J. Stebe, *Soft Matter*, 2012, 9, 779–786, DOI: 10.1039/ C2SM27020J.
- 97 B. J. Park and E. M. Furst, Soft Matter, 2011, 7, 7676–7682, DOI: 10.1039/C1SM00005E.
- 98 A. Kumar, B. J. Park, F. Tu and D. Lee, *Soft Matter*, 2013, 9, 6604–6617, DOI: 10.1039/C3SM50239B.
- 99 P. A. Kralchevsky, N. D. Denkov and K. D. Danov, *Langmuir*, 2001, 17, 7694–7705, DOI: 10.1021/la0109359.
- 100 P. A. Kralchevsky, V. N. Paunov, N. D. Denkov, I. B. Ivanov and K. Nagayama, *J. Colloid Interface Sci.*, 1993, 155, 420–437, DOI: 10.1006/jcis.1993.1056.
- 101 P. A. Kralchevsky, V. N. Paunov, I. B. Ivanov and K. Nagayama, J. Colloid Interface Sci., 1992, 151, 79–94, DOI: 10.1016/0021-9797(92)90239-I.
- 102 P. A. Kralchevsky and K. Nagayama, Adv. Colloid Interface Sci., 2000, 85, 145–192, DOI: 10.1016/S0001-8686(99)00016-0.
- 103 P. A. Kralchevsky and K. Nagayama, *Langmuir*, 1994, **10**, 23–36, DOI: **10.1021/la00013a004**.
- 104 P. A. Kralchevsky and N. D. Denkov, *Curr. Opin. Colloid Interface Sci.*, 2001, **6**, 383–401, DOI: **10.1016/S1359-0294(01)00105-4**.
- 105 F. Bresme and M. Oettel, *J. Phys.: Condens. Matter*, 2007, **19**, 413101, DOI: **10.1088/0953-8984/19/41/413101**.
- 106 Y. Lin, H. Skaff, T. Emrick, A. D. Dinsmore and T. P. Russell, Science, 2003, 299, 226–229, DOI: 10.1126/science.1078616.
- 107 B. G. Prevo and O. D. Velev, *Langmuir*, 2004, **20**, 2099–2107, DOI: **10.1021/la035295j**.
- 108 B. G. Prevo, Y. Hwang and O. D. Velev, *Chem. Mater.*, 2005, 17, 3642–3651, DOI: 10.1021/cm050416h.
- 109 V. N. Paunov, P. A. Kralchevsky, N. D. Denkov and K. Nagayama, J. Colloid Interface Sci., 1993, 157, 100–112, DOI: 10.1006/jcis.1993.1163.
- 110 V. N. Paunov, P. A. Kralchevsky, N. D. Denkov, I. B. Ivanov and K. Nagayama, *Colloids Surf.*, 1992, 67, 119–138, DOI: 10.1016/0166-6622(92)80292-A.
- 111 P. A. Kralchevsky and V. N. Paunov, *J. Fluid Mech.*, 1995, **299**, 105–132, DOI: **10.1017/S0022112095003442**.
- 112 D. Y. C. Chan, J. D. Henry and L. R. White, J. Colloid Interface Sci., 1981, 79, 410-418, DOI: 10.1016/0021-9797(81)90092-8.

- 113 J. C. Loudet, A. M. Alsayed, J. Zhang and A. G. Yodh, *Phys. Rev. Lett.*, 2005, **94**, 018301, DOI: **10.1103/PhysRev Lett.94.018301**.
- 114 E. P. Lewandowski, M. Cavallaro, L. Botto, J. C. Bernate, V. Garbin and K. J. Stebe, *Langmuir*, 2010, 26, 15142–15154, DOI: 10.1021/la1012632.
- 115 S. Zhao, Y. Wu, W. Lu and B. Liu, *ACS Macro Lett.*, 2019, **8**, 363–367, DOI: **10.1021/acsmacrolett.8b00985**.
- 116 B. Bharti, D. Rutkowski, K. Han, A. U. Kumar, C. K. Hall and O. D. Velev, *J. Am. Chem. Soc.*, 2016, **138**, 14948–14953, DOI: **10.1021/jacs.6b08017**.
- 117 E. Koos, *Curr. Opin. Colloid Interface Sci.*, 2014, **19**, 575–584, DOI: **10.1016/j.cocis.2014.10.004**.
- 118 S. Roh, D. P. Parekh, B. Bharti, S. D. Stoyanov and O. D. Velev, *Adv. Mater.*, 2017, **29**, 1701554, DOI: **10.1002**/ **adma.201701554**.
- 119 E. Koos, J. Johannsmeier, L. Schwebler and N. Willenbacher, *Soft Matter*, 2012, **8**, 6620–6628, DOI: **10.1039/c2sm25681a**.
- 120 N. Bowden, A. Terfort, J. Carbeck and G. M. Whitesides, Science, 1997, 276, 233–235, DOI: 10.1126/science.276. 5310.233.
- 121 N. Bowden, F. Arias, T. Deng and G. M. Whitesides, *Langmuir*, 2001, **17**, 1757–1765, DOI: **10.1021/la0014470**.
- 122 L. Botto, L. Yao, R. L. Leheny and K. J. Stebe, *Soft Matter*, 2012, **8**, 4971–4979, DOI: **10.1039/c2sm25211b**.
- 123 B. Madivala, J. Fransaer and J. Vermant, *Langmuir*, 2009, 25, 2718–2728, DOI: 10.1021/la803554u.
- 124 Q. Wang, J. Yu, K. Yuan, L. Yang, D. Jin and L. Zhang, Appl. Mater. Today, 2020, 18, 100489, DOI: 10.1016/j.apmt. 2019.100489.
- 125 F. Li, S. A. Delo and A. Stein, *Angew. Chemie*, 2007, **119**, 6786–6789, DOI: **10.1002/ange.200701553**.
- 126 X. Zheng, M. Liu, M. He, D. J. Pine and M. Weck, Angew. Chem., Int. Ed., 2017, 56, 5507–5511, DOI: 10.1002/anie. 201701456.
- 127 L. Tian, Y. Liu, D. Wang, J. Tan, Y. Xie, B. Li, Q. Zhang, C. Zhu and J. Xu, *Polym. Chem.*, 2022, 13, 1084–1089, DOI: 10.1039/d1py00360g.
- 128 D. J. Kraft, W. S. Vlug, C. M. Van Kats, A. Van Blaaderen, A. Imhof and W. K. Kegel, *J. Am. Chem. Soc.*, 2009, 131, 1182–1186, DOI: 10.1021/ja8079803.
- 129 E. Koos and N. Willenbacher, *Science*, 2011, **331**, 897–900, DOI: **10.1126/science.1199243**.
- 130 H. Ding, S. Barg and B. Derby, *Nanoscale*, 2020, **12**, 11440–11447, DOI: **10.1039/c9nr10831a**.
- 131 S. Van Kao, L. E. Nielsen and C. T. Hill, *J. Colloid Interface Sci.*, 1975, 53, 367–373, DOI: 10.1016/0021-9797(75)90052-1.
- 132 F. Bossler and E. Koos, *Langmuir*, 2016, 32, 1489–1501, DOI: 10.1021/acs.langmuir.5b04246.
- 133 F. Bossler, L. Weyrauch, R. Schmidt and E. Koos, *Colloids Surf.*, A, 2017, 518, 85–97, DOI: 10.1016/j.colsurfa. 2017.01.026.
- 134 S. Hoffmann, E. Koos and N. Willenbacher, *Food Hydrocolloids*, 2014, **40**, 44–52, DOI: **10.1016/j.foodhyd.2014**. **01.027**.

- 135 J. Allard, S. Burgers, M. C. Rodríguez González, Y. Zhu, S. De Feyter and E. Koos, *Colloids Surf.*, A, 2022, 648, 129224, DOI: 10.1016/j.colsurfa.2022.129224.
- 136 M. Schneider, E. Koos and N. Willenbacher, *Sci. Rep.*, 2016, 6, 1–10, DOI: 10.1038/srep31367.
- 137 J. Maurath and N. Willenbacher, *J. Eur. Ceram. Soc.*, 2017, 37, 4833–4842, DOI: 10.1016/j.jeurceramsoc.2017.06.001.
- 138 M. L. Sesso, S. Slater, J. Thornton and G. V. Franks, *J. Am. Ceram. Soc.*, 2021, **104**, 4977–4990, DOI: **10.1111/jace.** 17911.
- 139 B. A. Grzybowski, H. A. Stone and G. M. Whitesides, Nature, 2000, 405, 1033–1036, DOI: 10.1038/35016528.
- 140 G. Grosjean, M. Hubert, Y. Collard, A. Sukhov, J. Harting,
 A. S. Smith and N. Vandewalle, *Soft Matter*, 2019, 15, 9093–9103, DOI: 10.1039/c9sm01414d.
- 141 M. Belkin, A. Snezhko, I. S. Aranson and W. K. Kwok, *Phys. Rev. Lett.*, 2007, **99**, 158301, DOI: **10.1103/PhysRevLett. 99.158301**.
- 142 A. Snezhko, I. S. Aranson and W. K. Kwok, *Phys. Rev. E: Stat., Nonlinear, Soft Matter Phys.*, 2006, 73, 041306, DOI: 10.1103/PhysRevE.73.041306.
- 143 J. Dobnikar, A. Snezhko and A. Yethiraj, *Soft Matter*, 2013, 9, 3693–3704, DOI: 10.1039/c3sm27363f.
- 144 A. Snezhko and I. S. Aranson, *Nat. Mater.*, 2011, **10**, 698–703, DOI: **10.1038/nmat3083**.
- 145 Q. Xie and J. Harting, *Adv. Mater.*, 2021, 33, 2006390, DOI: 10.1002/adma.202006390.
- 146 G. B. Davies, T. Krüger, P. V. Coveney, J. Harting and F. Bresme, *Soft Matter*, 2014, **10**, 6742–6748, DOI: **10.1039**/ **c4sm01124d**.
- 147 J. Faraudo and F. Bresme, *J. Chem. Phys.*, 2003, **118**, 6518–6528, DOI: **10.1063/1.1559728**.
- 148 F. Bresme and J. Faraudo, *J. Phys.: Condens. Matter*, 2007, 19, 375110, DOI: 10.1088/0953-8984/19/37/375110.
- 149 Q. Xie, G. B. Davies, F. Günther and J. Harting, *Soft Matter*, 2015, **11**, 3581–3588, DOI: **10.1039**/c**5sm00255a**.
- 150 Q. Xie, G. B. Davies and J. Harting, *Soft Matter*, 2016, **12**, 6566–6574, DOI: **10.1039/c6sm01201a**.
- 151 B. Bharti, A. L. Fameau and O. D. Velev, *Faraday Discuss.*, 2015, **181**, 437–448, DOI: **10.1039/c4fd00272e**.
- 152 J. Zhou, L. Wang, X. Qiao, B. P. Binks and K. Sun, J. Colloid Interface Sci., 2012, 367, 213–224, DOI: 10.1016/j.jcis. 2011.11.001.
- 153 J. Zhou, X. Qiao, B. P. Binks, K. Sun, M. Bai, Y. Li and Y. Liu, *Langmuir*, 2011, 27, 3308–3316, DOI: 10.1021/la1036844.
- 154 A. L. Fameau, A. Carl, A. Saint-Jalmes and R. Von Klitzing, *ChemPhysChem*, 2015, **16**, 66–75, DOI: **10.1002/cphc.2014 02580**.
- 155 D. Davino, M. D'auria, R. Pantani and L. Sorrentino, *Polymers*, 2021, 23, 1–18, DOI: 10.3390/polym13010024.
- 156 J. A. Rodrigues, E. Rio, J. Bobroff, D. Langevin and W. Drenckhan, *Colloids Surf.*, *A*, 2011, **384**, 408–416, DOI: **10.1016/j.colsurfa.2011.04.029**.
- 157 K. Soetanto and H. Watarai, *Jpn. J. Appl. Phys., Part 1*, 2000, **39**, 3230–3232, DOI: **10.1143/jjap.39.3230**.

- 158 A. L. Campbell, S. D. Stoyanov and V. N. Paunov, *Soft Matter*, 2009, **5**, 1019–1023, DOI: **10.1039/b812706a**.
- 159 X. Zhao, P. A. Quinto-Su and C. D. Ohl, *Phys. Rev. Lett.*, 2009, **102**, 024501, DOI: **10.1103/PhysRevLett.102.024501**.
- 160 A. L. Fameau and S. Fujii, Curr. Opin. Colloid Interface Sci., 2020, 50, 101380, DOI: 10.1016/j.cocis.2020.08.005.
- 161 S. Hutzler, D. Weaire, F. Eliás and E. Janiaud, *Philos. Mag. Lett.*, 2002, 82, 297–301, DOI: 10.1080/09500830210128074.
- 162 E. Blanco, S. Lam, S. K. Smoukov, K. P. Velikov, S. A. Khan and O. D. Velev, *Langmuir*, 2013, 29, 10019–10027, DOI: 10.1021/la4014224.
- 163 A. L. Fameau, S. Lam and O. D. Velev, *Chem. Sci.*, 2013, 4, 3874–3881, DOI: 10.1039/c3sc51774h.
- 164 N. I. Castellanos, B. Bharti and O. D. Velev, *J. Phys. Chem. B*, 2021, **125**, 7900–7910, DOI: **10.1021/acs.jpcb.1c03158**.
- 165 S. Lam, E. Blanco, S. K. Smoukov, K. P. Velikov and O. D. Velev, *J. Am. Chem. Soc.*, 2011, 133, 13856–13859, DOI: 10.1021/ja205065w.
- 166 A. Kaiser, T. Liu, W. Richtering and A. M. Schmidt, Langmuir, 2009, 25, 7335–7341, DOI: 10.1021/la900401f.
- 167 A. L. Fameau, S. Lam, A. Arnould, C. Gaillard, O. D. Velev and A. Saint-Jalmes, *Langmuir*, 2015, 31, 13501–13510, DOI: 10.1021/acs.langmuir.5b03660.
- 168 A. M. Menzel, J. Chem. Phys., 2014, 141, 194907, DOI: 10.1063/1.4901275.
- 169 O. N. Sorokina, A. L. Kovarski, M. A. Lagutina, S. A. Dubrovskii and F. S. Dzheparov, *Appl. Sci.*, 2012, 2, 342–350, DOI: 10.3390/app2020342.
- 170 M. Yu, B. Ju, J. Fu, S. Liu and S. B. Choi, *Ind. Eng. Chem. Res.*, 2014, 53, 4704–4710, DOI: 10.1021/ie4040237.
- 171 K. Lalitha, Y. S. Prasad, V. Sridharan, C. U. Maheswari, G. John and S. Nagarajan, *RSC Adv.*, 2015, **5**, 77589–77594, DOI: **10.1039/c5ra14744a**.
- 172 M. Tarama, P. Cremer, D. Y. Borin, S. Odenbach, H. Löwen and A. M. Menzel, *Phys. Rev. E: Stat., Nonlinear, Soft Matter Phys.*, 2014, **90**, 42311, DOI: **10.1103/PhysRevE.90.042311**.
- 173 A. Stoll, M. Mayer, G. J. Monkman and M. Shamonin, *J. Appl. Polym. Sci.*, 2014, **131**, 39793, DOI: **10.1002**/app.39793.
- 174 J. Chatterjee, Y. Haik and C. J. Chen, *Colloid Polym. Sci.*, 2003, **281**, 892–896, DOI: **10.1007/s00396-003-0916-z**.
- 175 J. Chatterjee, Y. Haik and C. J. Chen, *J. Appl. Polym. Sci.*, 2004, **91**, 3337–3341, DOI: **10.1002/app.13545**.
- 176 S. A. Braim, K. M. Shakesheff, B. R. Saunders and C. Alexander, *J. Mater. Chem. B*, 2016, **4**, 962–972, DOI: **10.1039/c5tb01739d**.
- 177 N. A. Jalili, M. Muscarello and A. K. Gaharwar, *Bioeng. Transl. Med.*, 2016, 1, 297–305, DOI: 10.1002/btm2.10034.
- 178 F. Ridi, M. Bonini and P. Baglioni, *Adv. Colloid Interface Sci.*, 2014, **207**, 3–13, DOI: **10.1016/j.cis.2013.09.006**.
- 179 A. Zadrail, V. Tokárová and F. Tpánek, *Soft Matter*, 2012, **8**, 1811–1816, DOI: **10.1039/c1sm06707a**.
- 180 X. Fan, X. Dong, A. C. Karacakol, H. Xie and M. Sitti, *Proc. Natl. Acad. Sci. U. S. A.*, 2020, 117, 27916–27926, DOI: 10.1073/PNAS.2016388117/SUPPL_FILE/PNAS.2016388117.SM06.MOV.

- 181 M. Sun, C. Tian, L. Mao, X. Meng, X. Shen, B. Hao, X. Wang, H. Xie and L. Zhang, Adv. Funct. Mater., 2022, 32, 2112508, DOI: 10.1002/ADFM.202112508.
- 182 X. Fan, M. Sun, L. Sun, H. Xie, X. Fan, M. Sun, L. Sun and H. Xie, Adv. Funct. Mater., 2020, 30, 2000138, DOI: 10.1002/ ADFM.202000138.
- 183 J. Čejková, T. Banno, M. M. Hanczyc and F. Štěpánek, Artif. Life, 2017, 23, 528-549, DOI: 10.1162/ARTL A 00243.
- 184 J. G. Lee, V. Porter, W. A. Shelton and B. Bharti, Langmuir, 2018, 34, 15416-15424, DOI: 10.1021/acs.langmuir.8b03232.
- 185 Z. Chen, D. Zhao, B. Liu, G. Nian, X. Li, J. Yin, S. Qu and W. Yang, Adv. Funct. Mater., 2019, 29, 1-8, DOI: 10.1002/ adfm.201900971.
- 186 A. Sydney Gladman, E. A. Matsumoto, R. G. Nuzzo, L. Mahadevan and J. A. Lewis, Nat. Mater., 2016, 15, 413-418, DOI: 10.1038/nmat4544.
- 187 Y. Kim, G. A. Parada, S. Liu and X. Zhao, Sci. Robot., 2019, 4, eaax7329, DOI: 10.1126/SCIROBOTICS.AAX7329.
- 188 S. Roh, L. B. Okello, N. Golbasi, J. P. Hankwitz, J. A. C. Liu, J. B. Tracy and O. D. Velev, Adv. Mater. Technol., 2019, 4, 1800528, DOI: 10.1002/admt.201800528.
- 189 Y. Kim and X. Zhao, Chem. Rev., 2022, 122, 5317-5364, DOI: 10.1021/acs.chemrev.1c00481.
- 190 Y. Kim, H. Yuk, R. Zhao, S. A. Chester and X. Zhao, Nature, 2018, 558, 274-279, DOI: 10.1038/s41586-018-0185-0.
- 191 C. Li, G. C. Lau, H. Yuan, A. Aggarwal, V. L. Dominguez, S. Liu, H. Sai, L. C. Palmer, N. A. Sather, T. J. Pearson, D. E. Freedman, P. K. Amiri, M. O. de la Cruz and S. I. Stupp, Sci. Robot., 2020, 5, eabb9822, DOI: 10.1126/scirobotics. abb9822.
- 192 M. Yu, B. Ju, J. Fu, S. Liu and S. B. Choi, Ind. Eng. Chem. Res., 2014, 53, 4704-4710, DOI: 10.1021/ie4040237.
- 193 D. Morales, B. Bharti, M. D. Dickey and O. D. Velev, Small, 2016, 12, 2283-2290, DOI: 10.1002/smll.201600037.
- 194 J. Yu, D. Jin, K. F. Chan, Q. Wang, K. Yuan and L. Zhang, Nat. Commun., 2019, 10, 1-12, DOI: 10.1038/s41467-019-13576-6.
- 195 J. Li, B. E. F. De Ávila, W. Gao, L. Zhang and J. Wang, Sci. Robot., 2017, 2, 6431, DOI: 10.1126/scirobotics.aam6431.
- 196 S. Kim, F. Qiu, S. Kim, A. Ghanbari, C. Moon, L. Zhang, B. J. Nelson and H. Choi, Adv. Mater., 2013, 25, 5863-5868, DOI: 10.1002/adma.201301484.
- 197 F. Qiu and B. J. Nelson, Engineering, 2015, 1, 021-026, DOI: 10.15302/J-ENG-2015005.

- 198 L. Li, Y. Zhu and J. Yang, Mater. Lett., 2018, 210, 136-138, DOI: 10.1016/j.matlet.2017.09.015.
- 199 H. Ravanbakhsh, G. Bao, Z. Luo, L. G. Mongeau and Y. S. Zhang, ACS Biomater. Sci. Eng., 2021, 7, 4009-4026, DOI: 10.1021/acsbiomaterials.0c01158.
- 200 S. S. Athukoralalage, R. Balu, N. K. Dutta and N. R. Choudhury, Polymers, 2019, 11, 898, DOI: 10.3390/polym11050898.
- 201 A. H. Williams, S. Roh, A. R. Jacob, S. D. Stoyanov, L. Hsiao and O. D. Velev, Nat. Commun., 2021, 12, 2834, DOI: 10.1038/s41467-021-23098-9.
- 202 D. Kokkinis, M. Schaffner and A. R. Studart, Nat. Commun., 2015, 6, 1-10, DOI: 10.1038/ncomms9643.
- 203 M. M. Schmauch, S. R. Mishra, B. A. Evans, O. D. Velev and J. B. Tracy, ACS Appl. Mater. Interfaces, 2017, 9, 11895-11901, DOI: 10.1021/acsami.7b01209.
- 204 J. Zhang, Z. Ren, W. Hu, R. H. Soon, I. C. Yasa, Z. Liu and M. Sitti, Sci. Robot., 2021, 6, 112, DOI: 10.1126/sciro botics.abf0112.
- 205 D. Jiao, C. Shi and G. De Schutter, Mater. Lett., 2022, 309, 131374, DOI: 10.1016/j.matlet.2021.131374.
- 206 Z. Varga, G. Filipcsei and M. Zrínyi, Polymer, 2006, 47, 227-233, DOI: 10.1016/j.polymer.2005.10.139.
- 207 S. R. Mishra, M. D. Dickey, O. D. Velev and J. B. Tracy, Nanoscale, 2016, 8, 1309-1313, DOI: 10.1039/c5nr07410j.
- 208 D. Morales, E. Palleau, M. D. Dickey and O. D. Velev, Soft Matter, 2014, 10, 1337-1348, DOI: 10.1039/c3sm51921j.
- 209 E. Palleau, D. Morales, M. D. Dickey and O. D. Velev, Nat. Commun., 2013, 4, 1-7, DOI: 10.1038/ncomms3257.
- 210 S. R. Mishra, M. D. Dickey, O. D. Velev and J. B. Tracy, Nanoscale, 2016, 8, 1309-1313, DOI: 10.1039/c5nr07410j.
- 211 M. Tarama, P. Cremer, D. Y. Borin, S. Odenbach, H. Löwen and A. M. Menzel, Phys. Rev. E: Stat., Nonlinear, Soft Matter Phys., 2014, 90, 042311, DOI: 10.1103/PhysRevE.90.042311.
- 212 H. N. An, B. Sun, S. J. Picken and E. Mendes, J. Phys. Chem. B, 2012, 116, 4702-4711, DOI: 10.1021/jp301482a.
- 213 Y. Wang, Y. Zhang, Y. Guan and Y. Zhang, Langmuir, 2022, 38, 6057-6065, DOI: 10.1021/acs.langmuir.2c00297.
- 214 Y. Guo, J. Zhang, W. Hu, M. T. A. Khan and M. Sitti, Nat. Commun., 2021, 12, 1-9, DOI: 10.1038/s41467-021-26136-8.
- 215 R. Sharma, S.-T. Chang and O. D. Velev, Langmuir, 2012, 28, 10128-10135, DOI: 10.1021/la301437f.
- 216 J. Deng, M. Molaei, N. G. Chisholm, T. Yao, A. Read and K. J. Stebe, Curr. Opin. Colloid Interface Sci., 2022, 61, 101629, DOI: 10.1016/j.cocis.2022.101629.