

Energy advances

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: J. Datta, N. Koratkar and D. Datta, *Energy Adv.*, 2024, DOI: 10.1039/D4YA00014E.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

Unlocking the Potential of Open-Tunnel Oxides: DFT-Guided Design and Machine Learning-Enhanced Discovery for Next- Generation Industry-Scale Battery Technologies

Joy Datta¹, Nikhil Koratkar², and Dibakar Datta^{1,*}

¹Department of Mechanical and Industrial Engineering, New Jersey Institute of Technology (NJIT), Newark, NJ 07052, USA

²Department of Mechanical, Aerospace, and Nuclear Engineering, Rensselaer Polytechnic Institute, Troy, New York, 12180, USA

Corresponding author: Dibakar Datta (dibakar.datta@njit.edu)

Abstract

Lithium-ion batteries (LIBs) are ubiquitous in everyday applications. However, Lithium (Li) is a limited resource on the planet and, therefore, not sustainable. As an alternative to lithium, earth-abundant and cheaper multivalent metals such as aluminum (Al) and calcium (Ca) have been actively researched in battery systems. However, finding suitable intercalation hosts for multivalent-ion batteries is urgently needed. Open-tunneled oxides represent a specific category of microparticles distinguished by the presence of integrated one-dimensional channels or nanopores. This work focuses on two promising open-tunnel oxides: niobium tungsten oxide (NTO) and molybdenum vanadium oxide (MoVO). The MoVO structure can accommodate a larger number of multivalent ions than NTO due to its larger surface area and different shapes. Specifically, the MoVO structure can adsorb Ca, Li, and Al ions with adsorption potentials ranging from around 4 to 5 eV. However, the adsorption potential for hexagonal channels of Al ion drops to 1.73 eV due to the limited channel area. The NTO structure exhibits an insertion/adsorption potential of 4.4 eV, 3.4 eV, and 0.9 eV for one Li, Ca, and Al, respectively. Generally, Ca ions are more readily adsorbed than Al ions in both MoVO and NTO structures. Bader charge analysis and charge density plots reveal the role of charge transfer and ion size in the insertion of multivalent ions such as Ca and Al into MoVO and NTO systems. Exploring open-tunnel oxide materials for battery applications is hindered by vast compositional possibilities. The execution of experimental trials and quantum-based simulations is not viable for addressing the challenge of locating a specific item within a large and complex set of possibilities. Therefore, it is imperative to conduct structural stability testing to identify viable combinations with sufficient pore topologies. Data mining and machine learning techniques are employed to discover innovative transitional metal oxide materials. This study compares two machine learning algorithms, one



utilizing descriptors and the other employing graphs to predict the synthesizability of new materials inside a laboratory setting. The outcomes of this study offer valuable insights into the exploration of alternative naturally occurring multiscale particles that exhibit promising potential for the utilization of multivalent ions in battery-related contexts.

Keywords: Open-Tunnel Oxides, Multivalent-Ion Batteries, Density Functional Theory, Data Mining, Machine Learning, Intercalation, Charge Transfer

1. INTRODUCTION

Rechargeable batteries, specifically secondary batteries, play a critical role in enabling the electrification of automobiles and the storage of energy from renewable sources such as wind and solar¹⁻³. However, the rising costs of rare-earth lithium have prompted a shift towards multivalent ions, such as aluminum, calcium, magnesium, and zinc. These ions are being investigated as substitutes for lithium-ion battery systems due to their abundant nature¹⁻⁸ and reduced degradation⁹ concerns. Consequently, a host material capable of withstanding the mechanical stresses induced by the insertion of multivalent ions is imperative for establishing multivalent-ion batteries as viable and competitive alternatives to lithium-ion batteries.

The selection of the active material's particle size used in the anode and cathode is crucial in affecting battery performance^{10,11}. Traditionally, microparticles have been used in the industry due to their higher volumetric energy density, high mass loading, better scalability, and lower cost¹². Nevertheless, microparticles encounter mechanics, thermodynamics, and kinetics challenges, all of which nanoparticles can solve¹³⁻¹⁵. Nanoparticles exhibit enhanced cycle stability over microparticles. Their smaller size allows for more uniform intercalation than microparticles, improving fracture toughness and fatigue life for electrode materials¹⁶⁻²⁰. Notably, nanoparticles also exhibit superior fast-charging capabilities. Their small size drastically reduces diffusion length, enabling faster charging and discharging ability^{21,22}. Furthermore, nanoparticles' limited compositional range makes them less conducive to the co-existence of distinct phases within nanostructures. Consequently, phase transitions occur more swiftly in nanostructures, releasing the excess free energy generated from lattice mismatch and high surface area²³⁻²⁵.

Nanostructures, however, come with their distinct set of drawbacks. For instance, the large surface area of nanostructures leads to extensive electrolyte decomposition. Consequently, the solid electrolyte interphase (SEI) layer forms early in the battery cycle, resulting in low first-cycle coulombic efficiency²⁶⁻³⁰. Additionally, achieving an industrial standard (20–30 mg/cm²) high mass loading (20–30 mg/cm²)



proves problematic with nanostructures^{31,32}. Nanostructure-based batteries also suffer from low volumetric capacity, significantly limiting their utility in stationary and grid storage applications^{19,33,34}. Moreover, the synthesis cost of nanostructures is higher, and the manufacturing process generates substantial chemical waste^{35–38}.

Multiscale particles (MP) embody nanoscale attributes within microscale particles, effectively combining characteristics of both micro and nanostructures¹³, potentially yielding the best of both worlds. These particles can be synthesized as engineered multiscale particles (E-MP) or multiscale particles with natural nano-porosity (N-MP). However, manufacturing cost and scalability pose significant challenges for E-MPs^{3,32}. On the other hand, micro-particles based on open-tunnel oxides, such as niobium tungsten oxide (NTO) and molybdenum vanadium oxide (MoVO), embody naturally formed nanoscale channels, endowing them with exceptionally fast ion diffusion abilities^{39,40}. N-MP family members display unique characteristics, exemplified by niobium tungsten oxide structures like Nb₁₂WO₃₃, Nb₁₆W₅O₅₅, and Nb₁₈W₁₆O₉₃^{41,42}. For example, Nb₁₂WO₃₃ is a wadsley-roth type crystallographic shear structure composed of (3×4) size of MO₆ (M=Nb, W) octahedral block⁴². These octahedral blocks share edges around the corner, forming open channel-like structures, as shown in Figure 1a. Kocer et al.⁴¹ investigated density functional theory (DFT) to identify Li insertion sites and scrutinized lattice contraction in the Nb₁₂WO₃₃ structure during high Li concentration, enhancing cycle stability. MoVO structures (Fig. 1b, c, d) can have different polymorphs - orthorhombic (MoV₂O₈), trigonal (MoV₃O₆), and tetragonal (MoVO₅). Furthermore, these structures feature additional tunnels like hexagonal, heptagonal, pentagonal, and rectangular varieties³⁹.

A thorough analysis of diverse materials is required to improve our understanding of open-tunnel oxide materials. The goal of this research is to uncover previously unknown chemicals that have the potential to surpass current ones. Pursuing an optimal solution through experimental trial and error is improbable, given the extensive range of possible material compositions and stoichiometries. This difficulty is compounded by complex and not fully understood reaction mechanisms^{43–45}. Hence, selecting the most appropriate candidate from the myriad options becomes a challenge akin to finding a 'needle in a haystack'⁹. Given the limited availability of known open-tunnel oxides with suitable pore sizes for accommodating multiply charged ions, a comprehensive exploration of new compounds becomes imperative.

Transition metal oxides (TMOs), especially at the nanoscale, possess distinctive structural characteristics essential for a wide range of applications⁴⁶. Nanotechnology enables precise control of TMO nanostructures, resulting in customized sizes and shapes with excellent surface area-to-volume ratios⁴⁷. Utilizing machine learning models trained on transition metal oxide (TMO) characteristics can aid in investigating various open tunnel oxides found in nature, drawing from knowledge and design concepts obtained from TMO nanostructures. Tunnel-structured transition metal oxides (TMOs) constitute a crucial



subgroup of TMOs with open channels enabling fast ion transport, including open tunnel oxides⁴⁸. Thus, a thorough understanding, and utilization of TMO-based oxide material training data provides critical insights for uncovering and investigating novel open tunnel oxide materials. This undertaking may encompass the study of binary, ternary, quaternary, quinary, and senary-based families of transition metal oxides (TMOs), a task laden with challenges due to the vast array of potential structures stemming from diverse combinations of elements and stoichiometries⁴⁹. The number of attainable materials reaches millions by varying the elements and stoichiometric ratios, rendering experimental exploration infeasible. Before selecting stable configurations with acceptable pore architectures for intercalating multiply charged ions, it is critical to analyze the structural stability of potential TMOs to assure their synthesizability⁴⁹.

To forecast the structural stability of TMOs, a DFT-based energy hull diagram can be constructed by evaluating the formation energy across all conceivable stoichiometric ratios⁹. However, the computationally intensive nature of this procedure is exacerbated by the intricate crystal structures and substantial unit cells of TMOs. Furthermore, addressing the "Needle in a Haystack" conundrum using DFT poses challenges due to the multitude of potential multivalent ion insertion sites and the potential for cation disorder^{50–52}. Molecular modeling employing the MD method presents a possible approach for exploring TMO crystal structures. Nonetheless, this approach hinges on the availability of a suitable interatomic potential, a requirement frequently unmet for oxide materials, constraining the MD method's capacity to explore all feasible combinations of TMO crystal structures. Furthermore, the reliability of the interatomic potential rests on data derived from DFT, which is not without limitations⁵³.

In recent years, deep learning algorithms such as graph neural networks (GNNs) have surfaced as a cost-effective avenue for predicting formation energy and band gap while establishing correlations between structure and properties^{54–57}. Compared to traditional methods, machine learning (ML) boasts two distinct advantages: compactness and the ability to predict the properties of numerous compounds within seconds without requiring substantial processing power. ML relies exclusively on information garnered from DFT and experimental techniques. Several databases, such as the materials project database (MPD)⁵⁸, open quantum materials database (OQMD)⁵⁹, automatic flow for materials discovery (AFLOW)⁶⁰, and inorganic crystal structure database (ICSD)⁶¹, provide the necessary crystal structure data for training and testing, as well as the corresponding property data that is utilized for the application of ML models.

Descriptor-based and GNN-based approaches have demonstrated strong predictive capabilities for material property forecasts^{56,62,63}. A "descriptor" comprises a numerical vector, employed as input for ML models in materials science, and encompasses diverse choices like coulomb matrix⁶⁴, sine coulomb matrix⁶⁵, atom-centered symmetry functions⁶⁶, smooth overlap of atomic orbitals⁶⁷, and orbital field matrix⁶⁸. In contrast, GNNs represent a category of deep learning techniques tailored to operate on graph



structures. The GNNs are extensively utilized in graph analysis because of their exceptional performance and interpretability. Multiple GNNs such as materials graph network (MEGNet)⁵⁶, atomistic line graph neural network (ALIGNN)⁶⁹, continuous graph neural networks (CGNN)⁷⁰, global attention based graph convolutional neural networks (GATGNN)⁵⁵, have exhibited strong prediction capabilities about material structures.

In contrast to the research mentioned above conducted with lithium (Li), there currently needs to be more available literature about the incorporation of multivalent ions, such as aluminum (Al) and calcium (Ca), into NTO or MoVO systems. In addition to that, we are extending our study from DFT-based investigations into a ML-focused approach, explicitly aiming to predict the formation energy of naturally occurring TMO. Our whole contribution to this work is organized in two interconnected sections -

1. We investigated the insertion of Ca, Al, and Li into trigonal structures (MoV_3O_6) that feature a variety of hexagonal, heptagonal, and triangular channels, thereby assessing their adsorption potential. Expanding our analysis, we also explored NTO ($\text{Nb}_{12}\text{WO}_{33}$) systems, enabling a comparison of the adsorption capabilities between NTO and MoVO structures. Moreover, we examined the influence of multivalent ion size and charge density on insertion potentials.
2. The preceding section utilized DFT to investigate certain TMOs recognized as stable and experimentally synthesizable. However, the potential number of stable TMOs is infinite, rendering it impossible to conduct DFT calculations for all possible combinations. In this section, we adopt a machine learning approach to identify potential stable TMOs by predicting their formation energy. To accomplish this, we used the MPD to compile an inorganic crystal structure dataset for TMOs. Using this dataset, we trained CNNs and GNNs to predict these materials' formation energy. The test dataset compared both models' performance. Once trained, these ML models allow experimentalists to estimate the synthesizability of unknown crystal structures. Furthermore, akin to the previous section, the predicted stable TMOs can be considered for further exploration via DFT studies in future investigations.



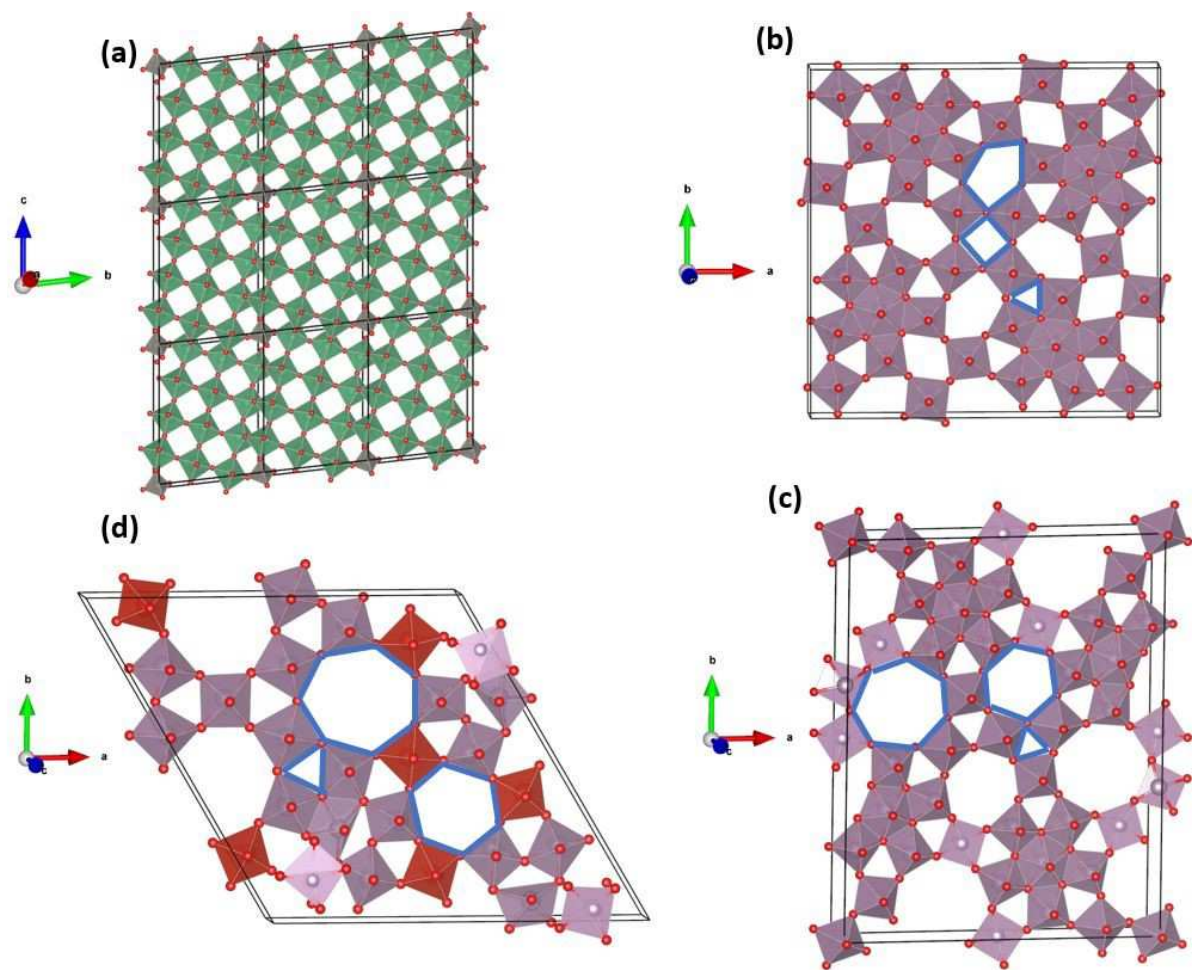


Figure 1: Crystal Structure of NMAM. (a) $\text{Nb}_{12}\text{WO}_{33}$ Structure: The block size is denoted as $(3 \times 4)\text{ReO}_3$. Every (3×4) block is connected by a niobium atom at the tetrahedral junctions and octahedral positions. These crystallographic edge-sharing structures generate channels. (b) Tetragonal (MoVO_5) structure consists of pentagonal, rectangular, and triangular channels. (c) Orthorhombic (MoV_2O_8) structure consists of heptagonal, hexagonal, and triangular channels. (d) Trigonal (MoV_3O_6) structure has a similar type of channel to the orthorhombic but with different atom numbers. All the channels in (b-d) are shown as blue. The channel dimensions of tetragonal MoVO (shown in b) are smaller than those of the orthorhombic and trigonal polymorphs (shown in c, d).

2. METHODS

2.1 DFT calculation



We employed DFT for structural optimization, utilizing the vienna ab initio simulation package (VASP)⁷¹ in conjunction with the projector augmented wave (PAW)⁷² method. The perdew–burke–ernzerhof (PBE)⁷³ formulation of the generalized gradient approximation (GGA) represents the exchange–correlation function. We employed an energy cut-off of 520 eV to represent the plane wave basis set. The k-point grid was utilized for Brillouin zone sampling. For molybdenum vanadium oxide (MoVO) and niobium tungsten oxide (NTO) structure, we employed 4×4×1 and 1×4×5 k-point grid, respectively. To relax the MoVO and NTO structures, we selected a force tolerance of 0.02 eV/Å and an energy-stopping criterion of 10^{−6} eV/Å.

The adsorption potential (V) is calculated as:

$$V = \frac{\Delta G}{n_f} \quad (1)$$

Where n_f is the concentration of Ca/Li/Al ion. The gibbs free energy, ΔG , is defined as:

$$\Delta G = \Delta E_f + P\Delta V_f - T\Delta S_f \quad (2)$$

In equation (2), at room temperature, $P\Delta V_f$ and $T\Delta S_f$ are very negligible compared to ΔE_f ¹⁰. The formation energy ΔE_f can be computed using the equation:

$$\Delta E_f = \Delta E_{X_nG} - (nE_x + E_g) \quad (3)$$

Where E_{X_nG} is the total energy of Ca/Li/Al-intercalated MoVO/NTO structure, E_x represents total energy of a single Ca/Li/Al ion, and E_g is the total energy of the MoVO/NTO structures. For this work, equilibrium energy of Ca and Li are -1.980 eV⁷⁴ and -1.8978 eV⁷⁵, respectively. We obtained the equilibrium energy of Al as -3.45 eV through DFT calculations.

2.2 Machine Learning Approach

2.2.1 Dataset Preparation

The dataset comprises 10123 inorganic structures of TMO-based compositions. It encompasses binary, ternary, quaternary, quinary, and senary TMO compositions. We utilize rigorous approaches to assess the structural characteristics of transition metal oxides (TMOs) in our dataset. We evaluated the void space of the 8098 training data structures using the VoronoiNN approach⁷⁶. Among these, 6500 structures had a void space larger than 0.5, suggesting a considerable number with significant empty spaces. This discovery indicates the capacity of the material to host ions or molecules, especially in situations where empty space is advantageous, such as in multivalent ion battery applications. We obtained packing fraction



data from the MPD to evaluate the level of porosity. 6190 structures have a packing fraction below 0.5, suggesting that most of them have low packing fractions and a significant level of porosity⁹. Materials with reduced packing fractions may have advantageous characteristics for ion diffusion and storage, which are essential for effective multivalent ion battery applications. The data distribution of these TMOs is illustrated in Figure 2a. We selectively picked the transitional metal data due to its relevance in the battery material industry. Notably, there are over 4000 datapoints for quaternary-based TMOs, while binary TMOs are the least represented, with only 313 datapoints (Figure 2a).

The dataset was retrieved from MP database utilizing the application programming interface (API) with the Matminer⁷⁷ and python materials genomics (pymatgen)⁷⁸ libraries in Python. Each data entry is associated with an ICSD ID, ensuring that these crystal structures are also present in the MP and ICSD databases. It is worth noting that the MP database includes a subset of naturally synthesizable ICSD materials^{78,79}.

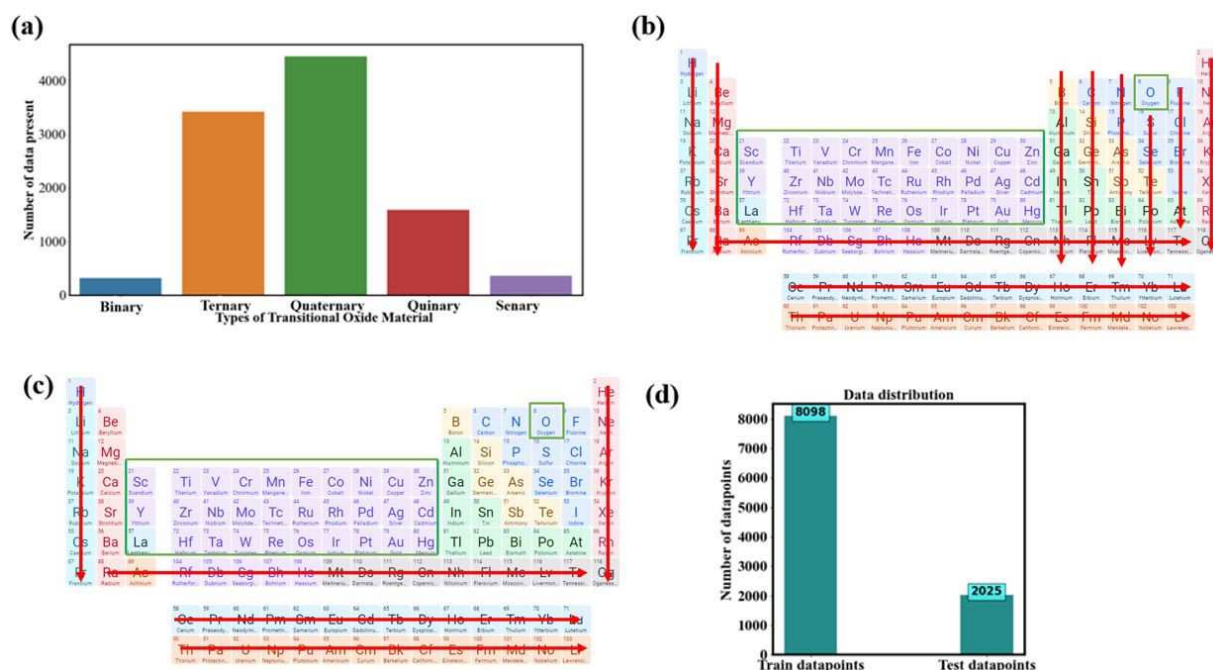


Figure 2: Data distribution of TMO based oxide material: (a) Number of data present concerning the number of TMOs material compositions, (b) Overview of binary TMOs, (c) Overview of ternary-based TMOs, (d) Training and testing data distribution for the ML model. In Figure 2(b,c), the green color represents the considered material, and red color depicts the ruled-out material from our list. Areas without color in Figure 2(c) represent the third element in ternary-based TMOs. Figure 2b shows the binary-based TMOs, where all transitional metals should be present, except for Oxygen(O). Figure 2c represents ternary-



based TMOs. In Figure 2c, multicomponent materials on TMO consist of elements from any element group except group 1 alkali metals, aligning with our focus on multivalent ions. For example, quaternary-based TMOs follow the format $W_sA_rB_mO_n$. Here, W represents any metal from the periodic table, excluding monovalent metals. A represents any metal from the periodic table. B represents the transitional metal. The s, r, m, and n, denote the stoichiometry ratio⁹. In our ML model, we allocated 80% of our randomly selected data to the training dataset, while the remaining 20% constitutes the testing dataset.

2.2.2 Convolutional Neural Network

Convolutional neural networks (CNNs) represent a form of deep learning technique capable of directly extracting intricate features from raw input data, rendering them suitable for various applications^{80,81}. Unlike fully connected neural networks, CNNs are more effective at recognizing natural structures through convolutional processes. CNNs incorporate convolution, pooling, fully connected, and dropout layers, collectively working to extract distinctive features and generate predictions.

In this work, we have selected the magpie descriptor and X-Ray diffraction pattern for our CNN input data. The descriptor simplifies feature extraction for supplementary applications by transforming these properties into a one-dimensional vector representation. The robust magpie descriptor technique^{82,83} allows for the calculation of various material properties, including physical, chemical, electrical, ionic, and fundamental characteristics.

The descriptor leverages a statistical analysis of the material's electrical structure, elemental composition, stoichiometric and elemental properties. Also, as part of its electronic structure properties, the descriptor contains information about electronic configuration, such as the typical proportion of electrons from each element's s, p, d, and f valences. The magpie descriptor has widespread applicability across numerous material science fields and can considerably improve the effectiveness and efficiency of materials research. The magpie features on pymatgen⁷⁸ library python with 132 dimensions represent a crystal structure's material properties.

Another descriptor is X-ray diffraction pattern, which plays a pivotal role in the experimental technique for determining the crystal structure of synthesized materials. It provides valuable insights into the atomic arrangement throughout the lattice. In the present dataset, we readily access XRD data from the MP Database⁵⁸ and incorporate it as one of the structure-based descriptors in this study. Previous work by Aguiar et al.⁸⁴ demonstrated using XRD descriptors for classifying the space group of crystal structures.



To incorporate XRD descriptors into our ML model for this study, we utilize the featurization tools provided by the Matminer library⁷⁷. The XRD featurizer transforms atomic positions into a one-dimensional (1D) array, effectively capturing essential crystal structure and phase information. The entire CNN architecture is depicted in Figure 3. We applied ReLU activation function after the convolutional layer and dropout after average pooling operation and dense operation to avoid overfitting.

To select the optimal hyperparameters, we employed bayesian optimization using the keras tuner library available in keras^{85–87}. Bayesian optimization has demonstrated remarkable effectiveness in determining the optimal hyperparameters for predicting material properties^{88,89}. Our technique involved dividing our datapoints into several subsets for the purposes of training and validation. More precisely, we employed an 80-20 division, allocating 80% of the data for training the model and reserving 20% of this training data for validation purposes during the hyperparameter tuning stage. The utilization of this validation set was crucial in fine-tuning the model's hyperparameters using bayesian optimization. The best hyperparameters were determined by evaluating the root mean square error (RMSE) on the validation dataset.

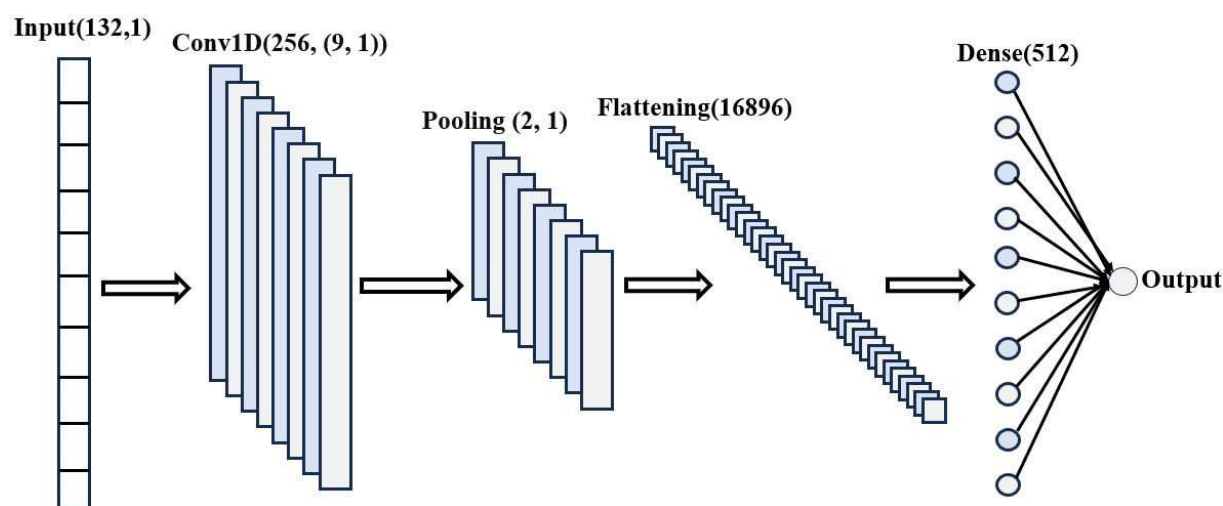


Figure 3: The CNN architecture incorporates the magpie featurizer as an input parameter. Hyperparameter optimization has been conducted to determine the ideal number of filters, the quantity of convolutional layers, the dropout rate, and the learning rate for predicting formation energy in eV/atom.

2.2.3 Graph Neural Network

This section focuses on presenting various graph neural network approaches for capturing crystal structure data, with a particular emphasis on predicting the formation energy of transition metal oxides (TMOs). To determine the optimal hyperparameters, we utilized a data partitioning strategy similar to that of the



descriptor-based approach. Our method involved dividing our dataset into distinct subsets for training and validation purposes. We adopted an 80-20 split, allocating 80% of the dataset for model training and reserving 20% of this training subset for validation during the hyperparameter optimization phase. TMO crystal structures are captured and predicted using different models, emphasizing atom and bond structure, atom alignment, and attention-based interactions.

2.2.3.1 MEGNet

The MEGNet framework, stands for materials graph network, is an implementation of graph networks for universal machine learning in materials science developed by DeepMind⁵⁶. The MEGNet architecture is constructed by stacking multiple MEGNet blocks. This architecture incorporates a dense layer that takes in three attributes: atomic state, binding state, and global state. The vectors are subsequently reduced and concatenated. MEGNet is essentially a sequence of update operations, facilitating the transformation from the initial graph $G = (E, V, u)$ to the updated graph $G^* = (E^*, V^*, u^*)$. The MEGNet structure comprises a series of MEGNet blocks that process atomic, binding, and global states, followed by vector reduction, concatenation, and update operations.

The MEGNet framework has been highly accurate in predicting molecular and crystalline properties using GNNs that can learn from the underlying structure of materials, including atoms, bonds, and crystal lattices. One of the main advantages of using GNNs is their ability to capture complex relationships among various atoms and their spatial arrangements.

2.2.3.2 DeeperGATGNN

DeeperGATGNN is an advanced GNN model designed to predict the properties of inorganic molecules⁹⁰. Building upon the successful GATGNN model⁵⁵, DeeperGATGNN addresses the challenge of over-smoothing, which limits the depth of the network. This limitation is overcome by incorporating additive skip-connections and differentiable group normalization (DGN) layers. The architecture of DeeperGATGNN comprises augmented graph attention (AGAT) layers, DGN operators, skip connections, a global attention layer, global pooling, and fully connected hidden layers. Through extensive experiments, DeeperGATGNN demonstrates superior performance compared to existing methods in predicting inorganic materials' properties. Furthermore, it provides interpretability by highlighting each atom's contribution. DeeperGATGNN represents a significant advancement in inorganic materials property prediction by effectively extracting inter-atomic-dependent features and overcoming the over-smoothing limitation.

2.2.3.3 ALIGNN



The ALIGNN model⁶⁹ utilizes edge-gated graph convolution⁹¹ to update the atomistic bond graph and its corresponding line graph. This model consists of two main parts: the bond graph and line graph. In bond graph, atoms are considered as nodes, and bonds are represented as edges, following a similar approach to the two models described earlier. The line graph, however, presents bonds as nodes, and edges connect pairs of bonds that share a common atom. This variant of graph convolution allows for aggregation of features from bond pairs and effective updates to atom and bond representations.

ALIGNN derives the atomistic line graph from the atomistic graph to incorporate angular information. Every node in the line graph corresponds to an edge in the original graph, representing interatomic bonds. The initial edge characteristics in the line graph are obtained through a radial basis function (RBF) expansion of the bond angle cosines. ALIGNN collects more details of atomic structure by incorporating angle information, improving its capacity to predict material properties.

The primary goal of ALIGNN is to develop a model that captures the complex interactions between atoms and bonds in crystal structures. By leveraging edge-gated graph convolution and incorporating angular information through the atomistic line graph, ALIGNN improves the accuracy of material property predictions. It provides a comprehensive representation of the atomic system, facilitating efficient information propagation between the atomistic bond graph and its line graph. This results in the effective capture of crucial features that influence material properties, particularly in crystals⁶⁹.

3. RESULTS AND DISCUSSION

3.1 DFT Analysis of Adsorption Potential and Charge Density

We inserted Ca into trigonal MoVO structures, specifically targeting three different types of channels: heptagonal, hexagonal, and triangular shapes¹¹. These channels contain 7-, 6-, and 3-membered rings, respectively. Identifying the most stable ion position within these channels is crucial. For this purpose, we strategically inserted Ca at various locations within the hexagonal and heptagonal tunnels, assessing the most stable position by comparing the energy of the optimized structures. The heptagonal and hexagonal channels have dimensions of approximately 5-6 Å, which are five times larger than the Ca ion (Ca^{2+})³⁹, making them well-suited for the intercalation of Ca, as depicted in Figure S1(b-f).

Given the limited space within the triangular tunnel, it can only accommodate a single Ca ion. To facilitate a clearer evaluation of the difference in adsorption potential, we inserted 2 Ca ions into both the heptagonal and hexagonal tunnels. For a single Ca ion, the heptagonal and hexagonal tunnels exhibited



nearly equivalent adsorption favorability of 4 eV (Figure S1b, c, g). Subsequently, we explored the insertion of 2 Ca ions into the heptagonal and hexagonal tunnels. In this case, the adsorption potential for the heptagonal and hexagonal channels is 3.06 eV and 2.07 eV, respectively. Consequently, the heptagonal channel emerged as the more favorable choice for Ca insertion compared to the other channels.

Given that Li has smaller charge density (Table 1) and size compared to Ca, we conducted a similar study using Li to investigate the influence of charge density and particle size. In this investigation, we explored the insertion of Li into both heptagonal and hexagonal channels, allowing Li to reposition itself to achieve the most optimized structure.

For the insertion of a single Li atom, the highest adsorption potential was observed within the heptagonal tunnel (4.73 eV, Figure S2a, f). Conversely, the lowest adsorption potential was found in the triangular channel (3.53 eV, Figure S2c, f). Figure S2f illustrates that even after introducing 2 Li atoms into both the heptagonal and hexagonal channels, the adsorption potential remains relatively high. The adsorption potential for the heptagonal and hexagonal channels is 4.22 eV and 3.46 eV, respectively. Consequently, the atomic size plays a significant role in enhancing the adsorption potential for 2 Li atoms (Figure S2f).

Al was introduced using the same intercalation process to assess the channels' comparative capabilities. However, when considering triangular channels (Figure S3c), Al could not be successfully inserted due to an unfavorable adsorption potential of -1.95 eV (Figure S3f). The highest adsorption favorability for a single Al atom is observed within the heptagonal channel (4.39 eV, Figure S3f). In contrast, the adsorption potential within the hexagonal tunnel is less than 50% compared to the heptagonal channel (Figure S3f). A larger channel size favors Al to achieve this high adsorption potential for the heptagonal channel (Figure S3f), which has 1.5 times more area in comparison with hexagonal channel. In the case of hexagonal channels, the ability to accommodate 2 Al atoms proved challenging because of low adsorption favorability (0.66 eV, Figure S3f).

Figure 4 presents a performance comparison of the adsorption capabilities of Ca, Li, and Al. Notably, Li exhibits the highest adsorption ability across various channel shapes. Ca demonstrates a nearly equivalent intercalation ability to Li, despite having a larger particle size compared to both Li and Al. However, as the channel dimensions decrease from heptagonal to triangular, Al exhibits a significantly poorer adsorption potential compared to Li and Ca (Figure 4(d)). This discrepancy can be primarily attributed to Al's notably high charge density (Table 1).



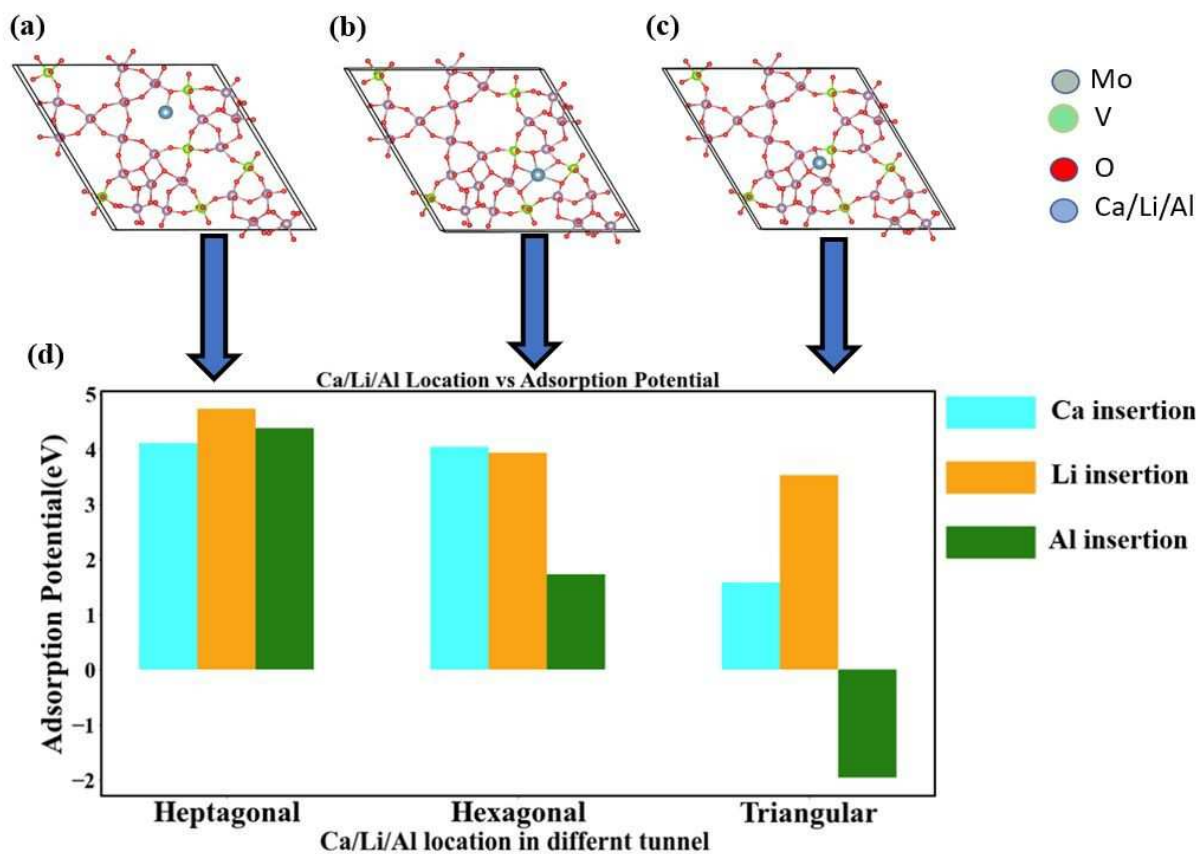


Figure 4. Comparative Analysis of the Adsorption Potential of Ca, Li, and Al Ions Across Different Tunnel Channels. Figure 4(a), 4(b), and 4(c) represent the locations of Ca, Li, and Al in heptagonal, hexagonal, and triangular channels, respectively. Figure 4(d) presents the comparison of adsorption potential concerning channel location. Notably, the adsorption potential remains consistent for the heptagonal channel, owing to its substantial channel dimensions. The pronounced impact of charge density becomes evident in the triangular channel.

Another multiscale particle with naturally occurring nanochannels is the NTO-based structure, with one of its family members being $\text{Nb}_{12}\text{WO}_{33}$ ^{41,42}. Similar to MoVO structures, we computed the adsorption potential for the insertion of Li, Ca, and Al into NTO using DFT. In $\text{Nb}_{12}\text{WO}_{33}$, there is a single rectangular-shaped channel available for insertion. We inserted Li, Ca, and Al into those channels at various concentrations (Figure 5a-f). For the insertion of 1 and 2 Li atoms, the adsorption potential (Figure 5g) is 4.4 eV and 3.44 eV, respectively. In contrast, 2 Ca and 2 Al atoms insertion into the channel resulted in the adsorption potential of -0.82 eV and -0.26 eV, respectively (Figure 5g). However, insertion favorability of 2 Ca and 2 Al is positive for the MoVO structure because heptagonal and hexagonal channels have areas of $41.67 \text{ \AA}^2$ and $27.19 \text{ \AA}^2$, respectively. However, for NTO, the area is only $15.36 \text{ \AA}^2$. These results indicate that channel area and charge density of cation (Table 2) play an important factor for adsorption favorability.



Our results indicate that inserting multivalent ions into the MoVO structure is more advantageous as compared to NTO.

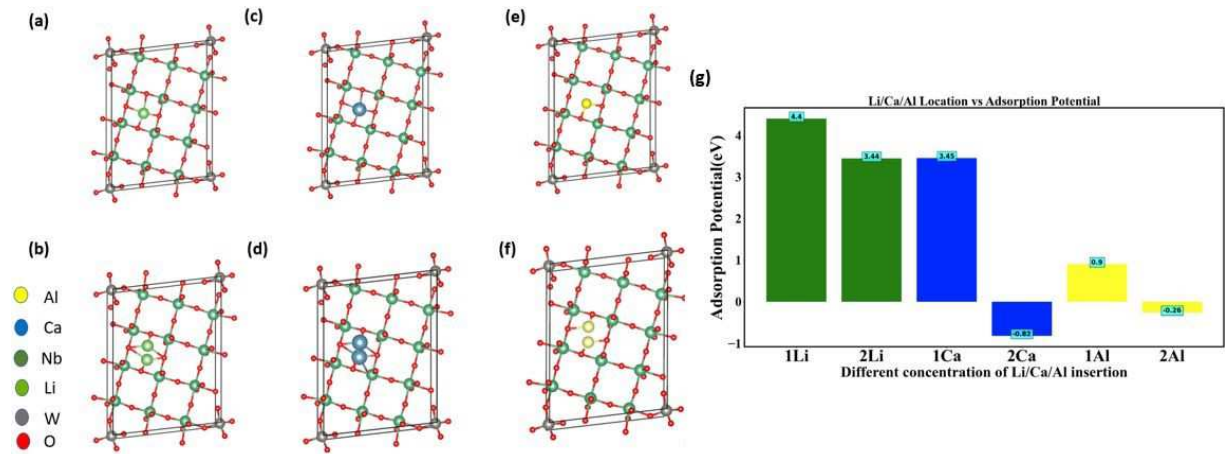


Figure 5. Inserting different concentrations of Li, Ca, and Al into the $Nb_{12}WO_{33}$ structure: (a) 1 Li, (b) 2 Li, (c) 1 Ca, (d) 2 Ca, (e) 1 Al, (f) 2 Al; (g) Examining the relationship between different concentrations of Li, Ca, and Al insertion and their respective adsorption potential. Notably, Li exhibits the highest adsorption potential, attributed to its smaller particle size and lower charge density when compared to Ca and Al.

To gain a comprehensive understanding of the charge distribution within the MoVO and NTO structures, we conducted Bader charge analysis and computed the charge density difference ($\Delta\rho$)⁹².

$$\Delta\rho = \rho_{A+B} - (\rho_A + \rho_B) \quad (4)$$

Here, 'A' represents the MoVO/NTO crystal structure, and 'B' signifies the cation inserted into this system.

ρ_A indicates the charge density of the MoVO/NTO crystal structures, while ρ_B represents the density of the cation. The Bader charge analysis has determined the number of charge transfers between cations and MoVO structures. Table 1 displays the results, showing that when 1 Al ion is inserted into a triangular channel, there is a charge transfer of 1.65 e/atom, which is higher than other cations. The charge density plot in Figure 6 illustrates the relationship between charge accumulation and depletion. In Figure 6m, Al ions exhibit the weakest interactions with all cations at these positions. Consequently, the negative adsorption potential observed in Figures S3 and 4 can be attributed to the lowest ionization of Al ion and MoVO structure at the triangular channel.

When contemplating the transfer of two ions, the charge transfer exhibits distinct characteristics owing to dipole-dipole interactions. These interactions can disturb the electronic structure of the atoms engaged in the exchange, causing modifications in electron density distribution. The redistribution of charges



significantly impacts the overall transfer of charge, as alterations in electron density directly influence the kinetics of charge transfer. Consequently, the charge transfer efficiency is lower for transferring two ions in the MoVO structure compared to sharing a single ion.

Charge transfer for NTO structures is highest for 1 Al ion (Table 2). Consequently, the adsorption potential is lowest for a single ion insertion (Figure 5g). Concerning two ions insertion, Ca exhibits the highest charge transfer relative to other cations (Table 2). Introducing two ions can elicit cooperative phenomena and facilitate a more extensive redistribution of charges inside the NTO structure. This can lead to more robust interactions with the host material and higher charge transfer compared to a scenario involving only a single ion. Consequently, the insertion of two Ca ions has the lowest potential for adsorption. In a broader context, our charge investigations reveal a negative correlation between the potential for adsorption and the extent of charge transfer within the NTO structure. An increase in charge transfer is inversely proportional to the degree of adsorption in the NTO structure.

Table 1: Calculated charge transfer from cation to the MoVO structures

	Ion name	Heptagonal 1 ion	Hexagonal 1 ion	Trigonal 1 ion	Heptagonal 2 ion	Hexagonal 2 ion
	Ca	1.08	1.57	1.42	1.22	1.25
Charge transfer (e/atom)	Li	0.55	0.69	0.63	0.38	0.46
	Al	1.28	1.04	1.65	1.06	1.26



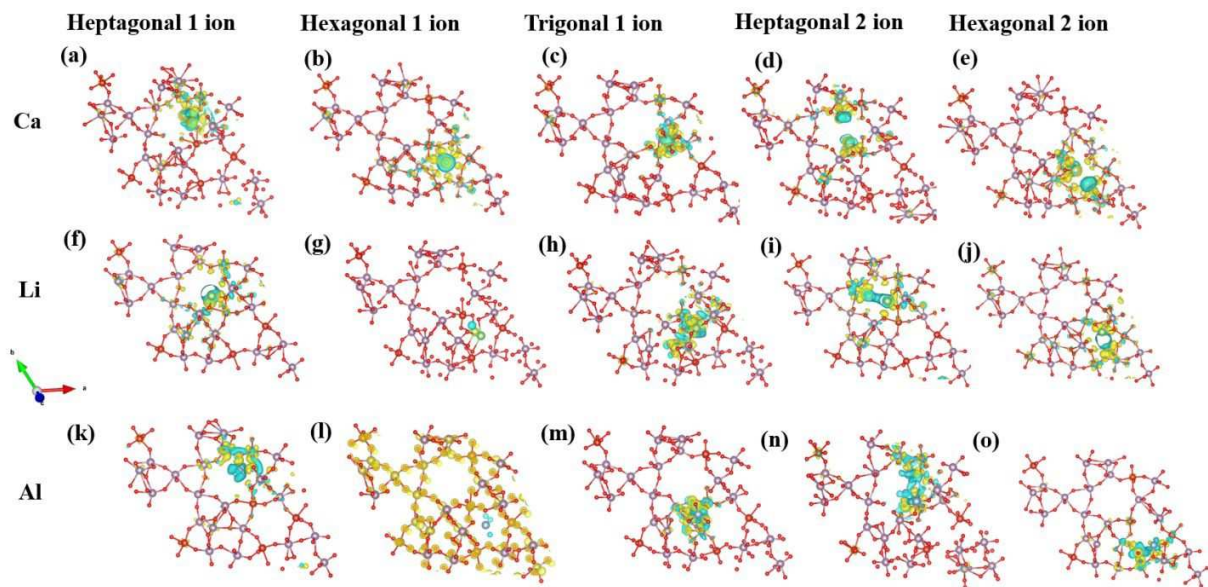


Figure 6: Charge Density Plot of the MoVO Structure for Ca, Li, and Al Ions: (a-c) 1 Ca insertion at various channel sites, (d, e) 2 Ca insertions at heptagonal and hexagonal channels, (f-g) 1 Li insertion at different channel sites, (i,j) 2 Li insertions at heptagonal and hexagonal channels, (k-m) 1 Al insertion at different channel sites, (n,o) 2 Al insertions at heptagonal and hexagonal channels. The isosurface level is set at $0.0045\text{ e}/\text{\AA}^3$. The yellow and cyan colors correspond to charge accumulation and charge depletion, respectively.

Table 2: Calculated charge transfer from cation to the NTO structures

	Ion name	1 ion	2 ions
Charge transfer (e/atom)	Ca	1.36	1.13
	Li	0.22	0.26
	Al	1.53	3.01




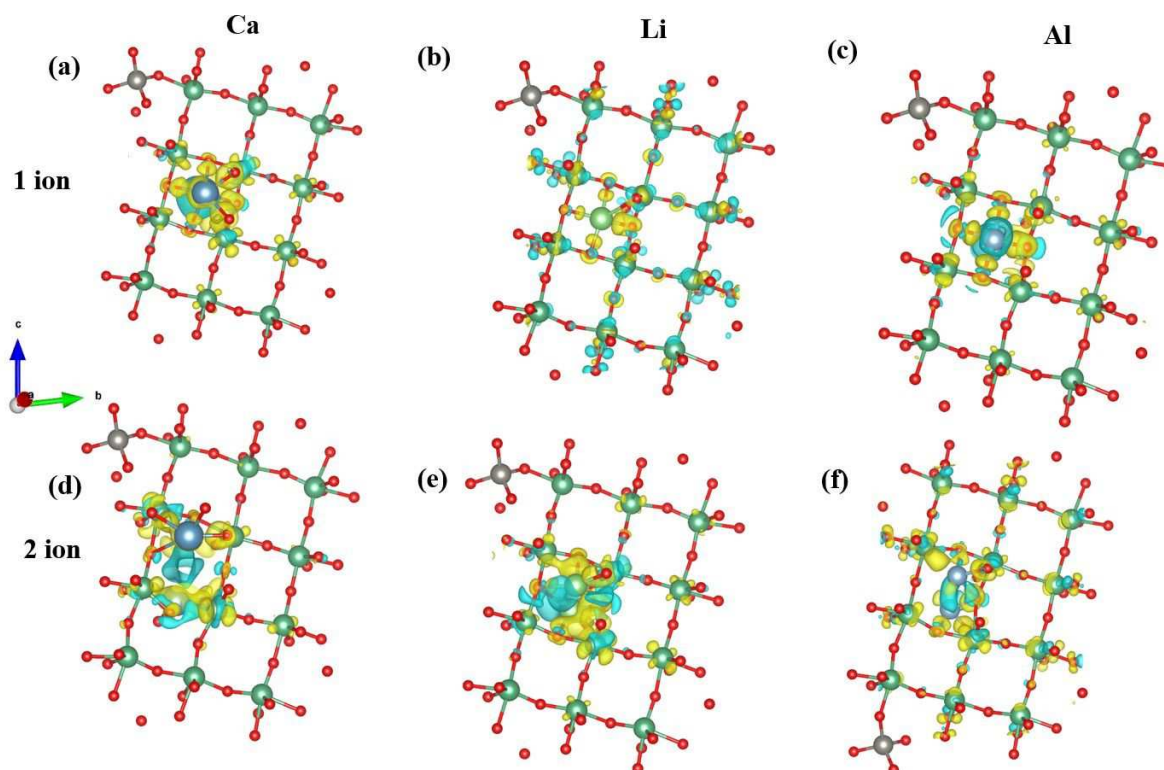


Figure 7: Charge Density Plot of the NTO Structure for Ca, Li, and Al Ions: (a-c) depict the scenario with 1 Ca/Li/Al insertion, (d, e) illustrate the scenario with 2 Ca/Li/Al insertions. The isosurface level is set at $0.0088 \text{ e}/\text{\AA}^3$. The yellow and cyan colors represent charge accumulation and charge depletion, respectively.

3.2 ML approach for discovering intercalation hosts:

We trained our input data using a CNN model that incorporates XRD patterns and magpie descriptors. In the process, we conducted an exhaustive search for optimal hyperparameters, encompassing various aspects such as the best convolutional layer, dense layer, number of nodes in each dense layer, learning rate, dropout rate, and optimizers. For magpie descriptors, the optimal architecture comprises a single convolution layer and one dense layer with 512 nodes. Conversely, when utilizing XRD featurizers, the best configuration entails two convolution layers and three dense layers with 512, 512, and 32 nodes, respectively. For both featurizers, we applied 1D average pooling to reduce spatial dimensionality of the input signal while retaining the essential features. We selected the ReLu activation function to accomplish the desired CNN outcomes. To mitigate overfitting, dropout rates ranging from 0.5 to 0.3 were implemented after each convolutional layer and dense layers.



We evaluated the validation dataset results for all two input data types to choose the best hyperparameters. In our research, we employ the commonly used RMSE metric for assessing prediction accuracy in predictive modeling. RMSE provides a numerical representation of the typical "distance" between model-predicted values and actual values, with lower RMSE values indicating a closer match to the data.

The RMSE values for the 2026 test dataset for 1-dimensional magpie descriptors and 1-dimensional XRD pattern are 0.25 eV/atom (see Figure 8b) and 0.56 eV/atom (see Figure 8a), respectively. Figure 8 displays the trendline between the actual and predicted values for the two descriptors. The x -axis in this scattering plot represents the actual formation energies, while the y -axis represents the predicted formation energies. The scatter plot in Figure 8 demonstrates the low variability or dispersion of predicted development forces compared to the calculated values. The dark data points in the graph represent the TMO materials with actual formation energies falling within the silicon range of -4.5 to 1.5 eV. Consequently, based on the 1-dimensional CNN model using these descriptors, magpie descriptors prove to be the more effective input data featurization approach for predicting the TMO-based formation energies (see Figure 8).

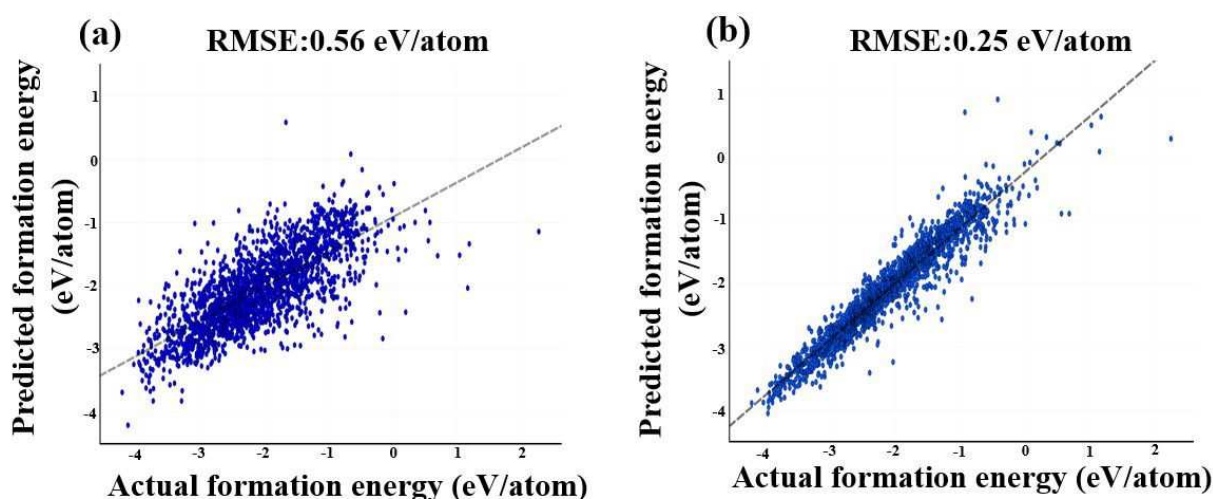


Figure 8: Visualization of CNN-Based Model Predictions, showcasing the relationship between actual and predicted values using two distinct featurization methods: (a) XRD patterns, and (b) Magpie descriptors. As evident from Figure 8(b), the magpie descriptors resulted in predictions that exhibited sparser and less pronounced deviations from the actual values, in contrast to the other featurization method.

In our pursuit of more accurate material property predictions, we explored the use of crystal-based graph conversion as our input data. For this purpose, we leveraged the MEGNet model, equipped with carefully



selected parameters: a batch size of 32, a learning rate of 0.00075, and an L2 regularization coefficient of 0.001. We conducted training for 300 epochs, keeping these parameters⁵⁶ consistent. Initially, we employed a cutoff radius of 5 Å to capture crystal structure interactions. However, recognizing the potential significance of long-range interactions, we expanded the cutoff radius to 6 Å to investigate their effects.

Interestingly, this modification did not yield a significant improvement in the model's performance. The system's predicted properties may be primarily influenced by short-range interactions, with long-range interactions playing a negligible role in this context. Furthermore, we employed an elemental embedding of 16 and selected three blocks to optimize the model's generalization capabilities. Although we experienced with different block numbers, ranging from 3 to 5, there is no substantial improvement in performance.

Figure 9 illustrates the MEGNet model's performance, using the same test dataset as the descriptor data, achieving an RMSE value of 0.13 eV/atom. This represents a significant improvement compared to the Magpie descriptors, where the RMSE value was 0.25 eV/atom. The performance of the MEGNet model is visualized in Figure 9(a).

As we considered the number of graph convolutional layer, it's important to note that an excessive increase in layers can lead to over-smoothing issues. DeeperGATGNN applies DGN and skip connections for training the data. Our implementation utilized a learning rate of 0.005 and batch size of 100. The model architecture consists of multiple layers, including a single pre-fully connected layer, several graph convolution layers, and no post fully connected layer. The model employs a "global_add_pool" pooling mechanism for effective global information aggregation and follows an "early" pooling order. The DeeperGATGNN model employs a graph representation with a maximum atomic interaction radius of 12 Å and a maximum of 12 neighboring atoms per atom, effectively capturing local atomic connectivity.

All training data underwent 300 epochs of training. To determine the optimal number of GNN layers, we studied with 10, 15 and 20 layers. Other parameters adhered to the default settings of DeeperGATGNN⁹⁰. Surprisingly, the best test RMSE value of 0.11 eV/atom was obtained with 10 GNN layers, beyond which the performance began to deteriorate, resulting in an RMSE value of 0.13 eV/atom for 15 and 20 GNN layers. This decline in performance can be attributed to the excessive increase in learning parameters when utilizing a larger number of GNN layers, which can hinder model performance, particularly with a limited training dataset. Figure 9b presents the performance of the DeeperGATGNN model.

In this study, we introduced the ALIGNN model, which leverages cutting-edge technology and complex algorithms to extract significant characteristics and properties of individual atoms within the molecular structure. This model comprises four alignment layers and four graph convolutional layers, with input features spanning 92-dimensional atomic attributes, 80 interatomic bond features, and 40 triplet input



features⁶⁹. As a result of the inconclusive outcomes observed when experimenting with different cutoff radius values, we decided to utilize the default value of 8Å in the ALIGNN model, which permits the inclusion of up to 12 adjacent atoms per atom⁶⁹.

By encoding the molecular structure into a lower-dimensional space using an embedding feature size of 64, the ALIGNN model efficiently extracts essential structural information and aligns molecular graphs. The inclusion of hidden features, set at 256, empowers the model to learn intricate patterns and representations effectively. For the ALIGNN model, the test RMSE is 0.11 eV/atom, underlining its exceptional predictive capabilities. Figure 9c represents the exemplary performance of the ALIGNN model.

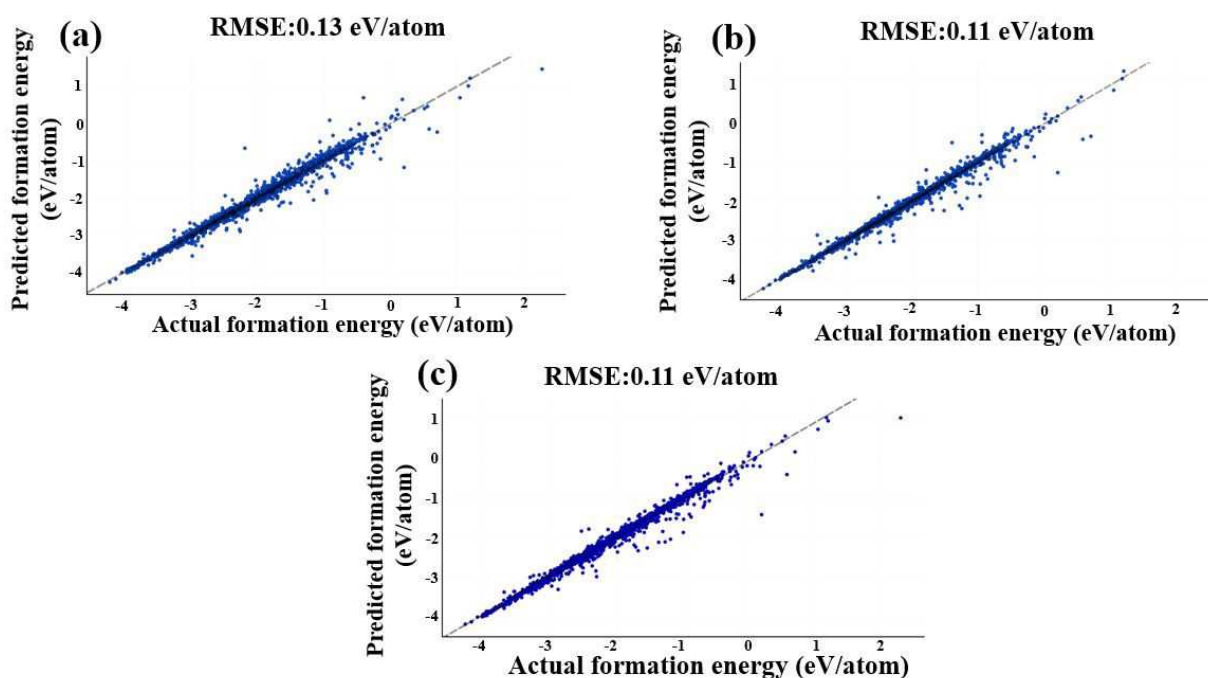


Figure 9: Performance Evaluation of GNN Models on the test dataset. The disparity between actual and predicted values is represented through scatter plots and trendlines for (a) MEGNet model, (b) DeeperGATGNN model, and (c) ALIGNN model. Notably, both the ALIGNN and DeeperGATGNN models outperform the human-crafted descriptors and the MEGNet model.

Figure 10a compares RMSE values between human-crafted descriptors and the GNN model. Notably, human-crafted descriptors appear to encompass critical structure-property relationships. Magpie descriptors stand out as the best performing, with an RMSE value of 0.25 eV/atom. However, the best RMSE value is obtained from ALIGNN and DeeperGATGNN models, both exhibiting an RMSE value of 0.11 eV/atom. This represents a remarkable 56% improvement in human-crafted descriptors. ALIGNN, in particular,



emerges as the top-performing model, achieving this exceptional RMSE value with fewer convolutional layers.

In contrast, the DeeperGATGNN model necessitates a more intricate hyperparameter optimization process, consuming computational resources, and time. ALIGNN distinguishes itself as the sole three-GNN model investigated in this study, preserving atom representations (one-body), bond representations (two-body), and bond angle representations (three-body). This distinguishing feature holds immense promise for capturing and portraying the periodic correlations inherent in crystal formations, thereby making a significant contribution to the field.

Figure 10b illustrates the distribution of mean absolute error (MAE) using ALIGNN. The analysis reveals that nearly 95% of the test samples (1933 instances) exhibit an error below 0.2 eV/atom, and half of the data showcases an error below this threshold. The overall average error, represented as the MAE, stands at approximately 0.05 eV/atom. Figure 10b provides a quantitative assessment of our model's performance, indicating that in 98.52% of cases, the model accurately predicts the formation energy/atom with an error below 0.40 eV/atom.

However, the ALIGNN model exhibits limitations in predicting the formation energy per atom for three specific structures (mp-690844, mp-1191949, mp-27873), as indicated by their higher MAE values exceeding 1. Upon detailed analysis, it becomes apparent that the graph representation employed by the ALIGNN model may not fully encapsulate the intricacies of interactions within these structures, leading to more pronounced prediction errors. One noteworthy observation from these cases is that ALIGNN primarily focuses on explicitly encoding three-body interactions. However, including higher-order n -body interactions (where n is greater than or equal to 4) could enhance the predictive capability of the ALIGNN model. Various studies in GNN have explored the incorporation of n -body interactions for diverse applications^{93–96}.

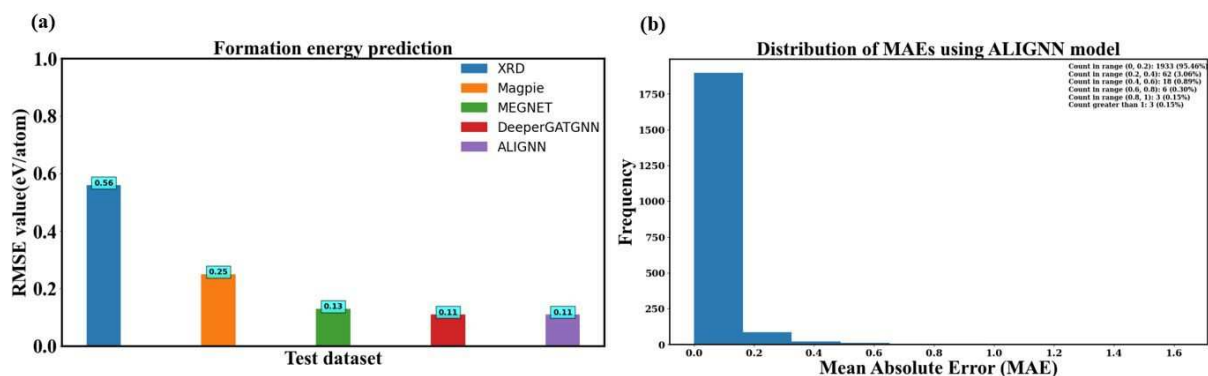


Figure 10: Test performance of our ML models. (a) Formation energy/atom prediction in terms of RMSE value. (b) Distribution of MAE value using ALIGNN model. The ALIGNN model, incorporating bond angle information, enables more accurate predictions with reduced errors, eliminating the requirement for extensive GNN layers. Over 95% of our predictions exhibit MAE values within the 0-0.2 range when employing the ALIGNN model.

4. CONCLUSIONS

We conducted first-principles calculations involving the insertion of both monovalent (Li) and multivalent (Ca, Al) species into multiscale oxide particles, characterized by one-dimensional nanochannels, exemplified by NTO and MoVO structures. A comparison of the adsorption potential of Ca, Li, and Al ions shows that the MoVO structure is more favorable to accommodate multivalent ions than NTO. The larger channel areas and different shapes of available channels, such as hexagonal, heptagonal, and triangular shapes, make MoVO a superior intercalation host for multivalent ions when compared to NTO structures.

The results from Bader charge analysis and charge density plots have unveiled that Al ions exhibit the lowest insertion favorability for both MoVO and NTO structures, primarily due to Al's substantial charge transfer to these materials. Meanwhile, Ca ions demonstrate adsorption behavior akin to monovalent Li ions but encounter challenges when inserted into the smaller channels of NTO structures, particularly when accommodating 2 Ca ions. Hence, it becomes evident that channel dimension, ion size, and ion charge density collectively play pivotal roles in the insertion of ions into MoVO and NTO structures. This deep understanding of ion insertion processes is critical for exploring materials with improved ion storage.

To lay the groundwork for future material screening methodologies, we gathered an extensive dataset of TMOs from the ICSD. The dataset has diverse structural compositions with empty spaces and nanochannels resembling those seen in NTO and MoVO structures, such open-tunnel oxides. In our research employing GNNs, we explored various methods for representing graphs. The ALIGNN and DeeperGATGNN models outperformed conventional descriptors, highlighting the effectiveness of graph-based representations in predicting formation energy. Based on these results, we aim to employ ML algorithms to forecast the stability of additional promising open-tunneled oxide materials for more efficient multivalent-ion batteries.

In the future, our focus will be on inverse machine learning (IML), a method that enables the creation of new crystal structures from TMOs^{9,97}. IML combined with our ML model holds great promise for predicting materials with specific characteristics including porosity, tunnel structure, formation energy, and



conductivity(Figure S3)⁹. The generative adversarial network (GAN) represents a potential approach IML, having successfully generated novel crystal structures with specific properties, expanding the scope of materials that can be developed beyond current databases⁹⁷.

Structures generated by IML can undergo further screening using our ML models to forecast stability, electronic and ionic conductivity, and pore sizes. By integrating ML with IML, we can effectively explore a wide variety of material parameters, leading to the identification of robust, conductive, and structurally strong intercalation hosts for multivalent-ion batteries. This approach simplifies the practical process of material screening, thereby advancing state-of-the-art materials for energy storage solutions.

AUTHOR INFORMATION

Corresponding Author

Dibakar Datta

Email: dibakar.datta@njit.edu

Phone: +1 973 596 3647

Author Contributions

D.D. and N.K. conceived the project. J.D. performed all work and wrote the manuscript with D.D. and N.K. All authors approved the final version of the manuscript.

CONFLICT OF INTEREST STATEMENT

The authors have no conflicts of interest to declare. All authors have seen and agree with the contents of the manuscript and there is no financial interest to report. We certify that the submission is original work and is not under review at any other publication.

ACKNOWLEDGEMENT

The work is supported by National Science Foundation (NSF) (Award Number # 2126180, # 2126178, #2237990). Authors acknowledge Advanced Cyberinfrastructure Coordination Ecosystem: Service & Support (ACCESS) for the computational facilities (Award Number - DMR180013).



DATA AVAILABILITY

Data can be obtained by requesting the corresponding author.

CODE AVAILABILITY

Code for extracting the data and its training model is available on GitHub

(<https://github.com/joy1303125/Graph-vs.-Descriptor-Approaches-for-Natural-Transition-Metal-Oxide-Discovery>), providing researchers in the field with a valuable resource. Restrictions apply to the availability of the simulation codes, which were used under license for this study.

References

- (1) Yoo, H. D.; Shterenberg, I.; Gofer, Y.; Gershinsky, G.; Pour, N.; Aurbach, D. Mg Rechargeable Batteries: An on-Going Challenge. *Energy Environ. Sci.* **2013**, 6 (8), 2265–2279.
- (2) Elia, G. A.; Marquardt, K.; Hoeppe, K.; Fantini, S.; Lin, R.; Knipping, E.; Peters, W.; Drillet, J.; Passerini, S.; Hahn, R. An Overview and Future Perspectives of Aluminum Batteries. *Adv. Mater.* **2016**, 28 (35), 7564–7579.
- (3) Muldoon, J.; Bucur, C. B.; Gregory, T. Quest for Nonaqueous Multivalent Secondary Batteries: Magnesium and Beyond. *Chem. Rev.* **2014**, 114 (23), 11683–11720.
- (4) Gummow, R. J.; Vamvounis, G.; Kannan, M. B.; He, Y. Calcium-ion Batteries: Current State-of-the-art and Future Perspectives. *Adv. Mater.* **2018**, 30 (39), 1801702.
- (5) Ponrouch, A.; Palacin, M. R. On the Road toward Calcium-Based Batteries. *Curr. Opin. Electrochem.* **2018**, 9, 1–7. <https://doi.org/10.1016/j.coelec.2018.02.001>.
- (6) Niloy, N. R.; Chowdhury, M. I.; Shanto, M. A. H.; Islam, J.; Rhaman, M. M. Multiferroic Bismuth Ferrite Nanocomposites as a Potential Photovoltaic Material. In *IOP Conference Series: Materials Science and Engineering*; IOP Publishing, 2021; Vol. 1091, p 12049.
- (7) Shanto, M. A. H.; Chowdhury, M. I.; Antu, A. B.; Niloy, N. R.; Alam, N.; Ullah, M. A.; Anwar, M. S. MXene Based Heterostructures for Electrode Materials of Batteries: A Review. In *IOP Conference Series: Materials Science and Engineering*; IOP Publishing, 2022; Vol. 1225, p 12018.
- (8) Vishnugopi, B. S. Mesoscale Physics of Electrified Interfaces with Metal Electrodes. Purdue



University 2023.

- (9) Lakhnot, A. S.; Panchal, R. A.; Datta, J.; Mahajani, V.; Bhimani, K.; Jain, R.; Datta, D.; Koratkar, N. Intercalation Hosts for Multivalent-Ion Batteries. *Small Struct.* **2022**, 2200290, 2200290. <https://doi.org/10.1002/ssstr.202200290>.
- (10) Chu, S.; Cui, Y.; Liu, N. The Path towards Sustainable Energy. *Nat. Mater.* **2017**, 16 (1), 16–22.
- (11) Chu, S.; Majumdar, A. Opportunities and Challenges for a Sustainable Energy Future. *Nature* **2012**, 488 (7411), 294–303.
- (12) Whittingham, M. S. History, Evolution, and Future Status of Energy Storage. *Proc. IEEE* **2012**, 100 (Special Centennial Issue), 1518–1534.
- (13) Jain, R.; Lakhnot, A. S.; Bhimani, K.; Sharma, S.; Mahajani, V.; Panchal, R. A.; Kamble, M.; Han, F.; Wang, C.; Koratkar, N. Nanostructuring versus Microstructuring in Battery Electrodes. *Nat. Rev. Mater.* **2022**, 7 (9), 736–746. <https://doi.org/10.1038/s41578-022-00454-9>.
- (14) Datta, J.; Datta, D.; Sharma, V. Transferable and Robust Machine Learning Model for Predicting Stability of Si Anodes for Multivalent Cation Batteries. *J. Mater. Sci.* **2023**, 58 (27), 11085–11099. <https://doi.org/10.1007/s10853-023-08705-y>.
- (15) Naik, K. G.; Vishnugopi, B. S.; Datta, J.; Datta, D.; Mukherjee, P. P. Electro-Chemo-Mechanical Challenges and Perspective in Lithium Metal Batteries. *Appl. Mech. Rev.* **2023**, 75 (1), 10802.
- (16) Qi, W.; Shapter, J. G.; Wu, Q.; Yin, T.; Gao, G.; Cui, D. Nanostructured Anode Materials for Lithium-Ion Batteries: Principle, Recent Progress and Future Perspectives. *J. Mater. Chem. A* **2017**, 5 (37), 19521–19540.
- (17) Graetz, J.; Ahn, C. C.; Yazami, R.; Fultz, B. Highly Reversible Lithium Storage in Nanostructured Silicon. *Electrochem. Solid-State Lett.* **2003**, 6 (9), A194.
- (18) Liu, X. H.; Zhong, L.; Huang, S.; Mao, S. X.; Zhu, T.; Huang, J. Y. Size-Dependent Fracture of Silicon Nanoparticles during Lithiation. *ACS Nano* **2012**, 6 (2), 1522–1531.
- (19) Shanto, M. A. H.; Niloy, N. R.; Islam, R.; Chowdhury, M. I.; Abrar, M. M.; Imam, S.-A. Effect of Channel Length and Dielectric Constant on Carbon Nanotube FET to Evaluate the Device Performance. In *2020 4th International Conference on Electronics, Materials Engineering & Nano-Technology (IEMENTech)*; IEEE, 2020; pp 1–4.
- (20) Uddin, M. S.; Mayanovic, R. A.; Benamara, M. On the Synthesis and Characterization of



Bimagnetic CoO/NiFe₂O₄ Heterostructured Nanoparticles. *AIP Adv.* **2023**, *13* (2).

- (21) Tang, Y.; Zhang, Y.; Li, W.; Ma, B.; Chen, X. Rational Material Design for Ultrafast Rechargeable Lithium-Ion Batteries. *Chem. Soc. Rev.* **2015**, *44* (17), 5926–5940.
- (22) Tsai, P.-C.; Wen, B.; Wolfman, M.; Choe, M.-J.; Pan, M. S.; Su, L.; Thornton, K.; Cabana, J.; Chiang, Y.-M. Single-Particle Measurements of Electrochemical Kinetics in NMC and NCA Cathodes for Li-Ion Batteries. *Energy Environ. Sci.* **2018**, *11* (4), 860–871.
- (23) Madej, E.; La Mantia, F.; Schuhmann, W.; Ventosa, E. Impact of the Specific Surface Area on the Memory Effect in Li-Ion Batteries: The Case of Anatase TiO₂. *Adv. Energy Mater.* **2014**, *4* (17), 1400829.
- (24) Van der Ven, A.; Wagemaker, M. Effect of Surface Energies and Nano-Particle Size Distribution on Open Circuit Voltage of Li-Electrodes. *Electrochem. commun.* **2009**, *11* (4), 881–884.
- (25) Guo, X.; Song, B.; Yu, G.; Wu, X.; Feng, X.; Li, D.; Chen, Y. Size-Dependent Memory Effect of the LiFePO₄ Electrode in Li-Ion Batteries. *ACS Appl. Mater. Interfaces* **2018**, *10* (48), 41407–41414.
- (26) Xu, K. Electrolytes and Interphases in Li-Ion Batteries and Beyond. *Chem. Rev.* **2014**, *114* (23), 11503–11618.
- (27) Keller, C.; Desrues, A.; Karuppiiah, S.; Martin, E.; Alper, J. P.; Boismain, F.; Villevieille, C.; Herlin-Boime, N.; Haon, C.; Chenevier, P. Effect of Size and Shape on Electrochemical Performance of Nano-Silicon-Based Lithium Battery. *Nanomaterials* **2021**, *11* (2), 307.
- (28) Lai, S. Y.; Knudsen, K. D.; Sejersted, B. T.; Ulvestad, A.; Mæhlen, J. P.; Koposov, A. Y. Silicon Nanoparticle Ensembles for Lithium-Ion Batteries Elucidated by Small-Angle Neutron Scattering. *ACS Appl. Energy Mater.* **2019**, *2* (5), 3220–3227.
- (29) Hundekar, P.; Basu, S.; Fan, X.; Li, L.; Yoshimura, A.; Gupta, T.; Sarbada, V.; Lakhnot, A.; Jain, R.; Narayanan, S. In Situ Healing of Dendrites in a Potassium Metal Battery. *Proc. Natl. Acad. Sci.* **2020**, *117* (11), 5588–5594.
- (30) Li, L.; Li, Z.; Yoshimura, A.; Sun, C.; Wang, T.; Chen, Y.; Chen, Z.; Littlejohn, A.; Xiang, Y.; Hundekar, P. Vanadium Disulfide Flakes with Nanolayered Titanium Disulfide Coating as Cathode Materials in Lithium-Ion Batteries. *Nat. Commun.* **2019**, *10* (1), 1764.
- (31) Wang, F.; Robert, R.; Chernova, N. A.; Pereira, N.; Omenya, F.; Badway, F.; Hua, X.; Ruotolo,



- M.; Zhang, R.; Wu, L. Conversion Reaction Mechanisms in Lithium Ion Batteries: Study of the Binary Metal Fluoride Electrodes. *J. Am. Chem. Soc.* **2011**, *133* (46), 18828–18836.
- (32) Courtney, I. A.; McKinnon, W. R.; Dahn, J. R. On the Aggregation of Tin in SnO Composite Glasses Caused by the Reversible Reaction with Lithium. *J. Electrochem. Soc.* **1999**, *146* (1), 59.
- (33) Karkar, Z.; Jaouhari, T.; Tranchot, A.; Mazouzi, D.; Guyomard, D.; Lestriez, B.; Roué, L. How Silicon Electrodes Can Be Calendered without Altering Their Mechanical Strength and Cycle Life. *J. Power Sources* **2017**, *371*, 136–147.
- (34) Sun, Y.-K.; Oh, S.-M.; Park, H.-K.; Scrosati, B. Micrometer-Sized, Nanoporous, High-Volumetric-Capacity $\text{LiMn}_{0.85}\text{Fe}_{0.15}\text{PO}_4$ Cathode Material for Rechargeable Lithium-Ion Batteries. *Adv. Mater.* **2011**, *23*.
- (35) Jung, S.-K.; Hwang, I.; Chang, D.; Park, K.-Y.; Kim, S. J.; Seong, W. M.; Eum, D.; Park, J.; Kim, B.; Kim, J. Nanoscale Phenomena in Lithium-Ion Batteries. *Chem. Rev.* **2019**, *120* (14), 6684–6737.
- (36) Berckmans, G.; Messagie, M.; Smekens, J.; Omar, N.; Vanhaverbeke, L.; Van Mierlo, J. Cost Projection of State of the Art Lithium-Ion Batteries for Electric Vehicles up to 2030. *Energies* **2017**, *10* (9), 1314.
- (37) Fan, X.; Zhu, Y.; Luo, C.; Suo, L.; Lin, Y.; Gao, T.; Xu, K.; Wang, C. Pomegranate-Structured Conversion-Reaction Cathode with a Built-in Li Source for High-Energy Li-Ion Batteries. *ACS Nano* **2016**, *10* (5), 5567–5577.
- (38) Hsu, K.-F.; Tsay, S.-Y.; Hwang, B.-J. Synthesis and Characterization of Nano-Sized LiFePO_4 Cathode Materials Prepared by a Citric Acid-Based Sol–Gel Route. *J. Mater. Chem.* **2004**, *14* (17), 2690–2695.
- (39) Lakhnot, A. S.; Bhimani, K.; Mahajani, V.; Panchal, R. A.; Sharma, S.; Koratkar, N. Reversible and Rapid Calcium Intercalation into Molybdenum Vanadium Oxides. *Proc. Natl. Acad. Sci. U. S. A.* **2022**, *119* (30). <https://doi.org/10.1073/pnas.2205762119>.
- (40) Lakhnot, A. S.; Gupta, T.; Singh, Y.; Hundekar, P.; Jain, R.; Han, F.; Koratkar, N. Aqueous Lithium-Ion Batteries with Niobium Tungsten Oxide Anodes for Superior Volumetric and Rate Capability. *Energy Storage Mater.* **2020**, *27*, 506–513. <https://doi.org/10.1016/j.ensm.2019.12.012>.
- (41) Koçer, C. P.; Griffith, K. J.; Grey, C. P.; Morris, A. J. Cation Disorder and Lithium Insertion



- Mechanism of Wadsley-Roth Crystallographic Shear Phases from First Principles. *J. Am. Chem. Soc.* **2019**, *141* (38), 15121–15134. <https://doi.org/10.1021/jacs.9b06316>.
- (42) Cava, R. J.; Murphy, D. W.; Zahurak, S. M. Lithium Insertion in Wadsley-Roth Phases Based on Niobium Oxide. *J. Electrochem. Soc.* **1983**, *130* (12), 2345–2351. <https://doi.org/10.1149/1.2119583>.
- (43) Aykol, M.; Montoya, J. H.; Hummelshøj, J. Rational Solid-State Synthesis Routes for Inorganic Materials. *J. Am. Chem. Soc.* **2021**, *143* (24), 9244–9259.
- (44) Chamorro, J. R.; McQueen, T. M. Progress toward Solid State Synthesis by Design. *Acc. Chem. Res.* **2018**, *51* (11), 2918–2925.
- (45) Turnbull, D.; Vonnegut, B. Nucleation Catalysis. *Ind. Eng. Chem.* **1952**, *44* (6), 1292–1298.
- (46) Meher, S. R. Transition Metal Oxide-Based Materials for Visible-Light-Photocatalysis. In *Nanostructured Materials for Visible Light Photocatalysis*; Elsevier, 2022; pp 153–183.
- (47) Banerjee, S.; De, B.; Sinha, P.; Cherusseri, J.; Kar, K. K. *Applications of Supercapacitors*; 2020; Vol. 300. https://doi.org/10.1007/978-3-030-43009-2_13.
- (48) Rao, C. N. R.; Rao, G. V. S. Transition Metal Oxides:: Crystal Chemistry, Phase Transition, and Related Aspects. **1974**.
- (49) Lakhnot, A. S.; Panchal, R. A.; Datta, J.; Mahajani, V.; Bhimani, K.; Jain, R.; Datta, D.; Koratkar, N. Intercalation Hosts for Multivalent-Ion Batteries. *Small Struct.* **2023**, *4* (4). <https://doi.org/10.1002/sstr.202200290>.
- (50) Rudberg, E.; Rubensson, E. H.; Salek, P. Kohn– Sham Density Functional Theory Electronic Structure Calculations with Linearly Scaling Computational Time and Memory Usage. *J. Chem. Theory Comput.* **2011**, *7* (2), 340–350.
- (51) Cohen, A. J.; Mori-Sánchez, P.; Yang, W. Challenges for Density Functional Theory. *Chem. Rev.* **2012**, *112* (1), 289–320.
- (52) Verma, P.; Truhlar, D. G. Status and Challenges of Density Functional Theory. *Trends Chem.* **2020**, *2* (4), 302–318.
- (53) He, X.; Zhu, Y.; Epstein, A.; Mo, Y. Statistical Variances of Diffusional Properties from Ab Initio Molecular Dynamics Simulations. *Npj Comput. Mater.* **2018**, *4* (1), 1–9.
- (54) Xie, T.; Grossman, J. C. Crystal Graph Convolutional Neural Networks for an Accurate and



- Interpretable Prediction of Material Properties. *Phys. Rev. Lett.* **2018**, *120* (14), 145301. <https://doi.org/10.1103/PhysRevLett.120.145301>.
- (55) Louis, S.-Y.; Zhao, Y.; Nasiri, A.; Wang, X.; Song, Y.; Liu, F.; Hu, J. Graph Convolutional Neural Networks with Global Attention for Improved Materials Property Prediction. *Phys. Chem. Chem. Phys.* **2020**, *22* (32), 18141–18148.
- (56) Chen, C.; Ye, W.; Zuo, Y.; Zheng, C.; Ong, S. P. Graph Networks as a Universal Machine Learning Framework for Molecules and Crystals. *Chem. Mater.* **2019**, *31* (9), 3564–3572.
- (57) bin Noor, M. F.; Yasmin, N.; Besara, T. Machine Learning in High-Entropy Alloys: Phase Formation Predictions with Artificial Neural Networks. *Futur. Sustain.* **2023**, *02*, 47–58. <https://doi.org/10.55670/fpll.fusus.2.1.5>.
- (58) Jain, A.; Ong, S. P.; Hautier, G.; Chen, W.; Richards, W. D.; Dacek, S.; Cholia, S.; Gunter, D.; Skinner, D.; Ceder, G.; Persson, K. A. Commentary: The Materials Project: A Materials Genome Approach to Accelerating Materials Innovation. *APL Mater.* **2013**, *1* (1). <https://doi.org/10.1063/1.4812323>.
- (59) Kirklin, S.; Saal, J. E.; Meredig, B.; Thompson, A.; Doak, J. W.; Aykol, M.; Rühl, S.; Wolverton, C. The Open Quantum Materials Database (OQMD): Assessing the Accuracy of DFT Formation Energies. *npj Comput. Mater.* **2015**, *1* (October). <https://doi.org/10.1038/npjcompumats.2015.10>.
- (60) Curtarolo, S.; Setyawan, W.; Hart, G. L. W.; Jahnatek, M.; Chepulskii, R. V.; Taylor, R. H.; Wang, S.; Xue, J.; Yang, K.; Levy, O. AFLOW: An Automatic Framework for High-Throughput Materials Discovery. *Comput. Mater. Sci.* **2012**, *58*, 218–226.
- (61) Karlsruhe, F. Inorganic Crystal Structure Database. URL <http://icsd.fiz-karlsruhe.de>. Accessed **2014**, 12.
- (62) Seko, A.; Togo, A.; Tanaka, I. Descriptors for Machine Learning of Materials Data. *arXiv Prepr. arXiv1709.01666* **2017**.
- (63) Himanen, L.; Jäger, M. O. J.; Morooka, E. V.; Federici Canova, F.; Ranawat, Y. S.; Gao, D. Z.; Rinke, P.; Foster, A. S. Dscribe: Library of Descriptors for Machine Learning in Materials Science. *Comput. Phys. Commun.* **2020**, *247*, 106949. <https://doi.org/10.1016/j.cpc.2019.106949>.
- (64) Rupp, M.; Tkatchenko, A.; Müller, K. R.; Von Lilienfeld, O. A. Fast and Accurate Modeling of Molecular Atomization Energies with Machine Learning. *Phys. Rev. Lett.* **2012**, *108* (5), 1–5. <https://doi.org/10.1103/PhysRevLett.108.058301>.



- (65) Faber, F. A.; Lindmaa, A.; Von Lilienfeld, O. A.; Armiento, R. Machine Learning Energies of 2 Million Elpasolite (ABC2D6) Crystals. *Phys. Rev. Lett.* **2016**, *117* (13), 2–7. <https://doi.org/10.1103/PhysRevLett.117.135502>.
- (66) Behler, J. Atom-Centered Symmetry Functions for Constructing High-Dimensional Neural Network Potentials. *J. Chem. Phys.* **2011**, *134* (7), 74106.
- (67) Bartók, A. P.; Kondor, R.; Csányi, G. On Representing Chemical Environments. *Phys. Rev. B* **2013**, *87* (18), 184115.
- (68) Pham, T. L.; Kino, H.; Terakura, K.; Miyake, T.; Tsuda, K. Machine Learning Reveals Orbital Interaction in Materials. *Sci. Technol. Adv. Mater.* **2017**, *6996* (November), 1–2. <https://doi.org/10.1080/14686996.2017.1378060>.
- (69) Choudhary, K.; DeCost, B. Atomistic Line Graph Neural Network for Improved Materials Property Predictions. *npj Comput. Mater.* **2021**, *7* (1), 185.
- (70) Xie, T.; Grossman, J. C. Crystal Graph Convolutional Neural Networks for an Accurate and Interpretable Prediction of Material Properties. *Phys. Rev. Lett.* **2018**, *120* (14), 145301.
- (71) Kresse, G.; Furthmüller, J. Efficient Iterative Schemes for Ab Initio Total-Energy Calculations Using a Plane-Wave Basis Set. *Phys. Rev. B* **1996**, *54* (16), 11169.
- (72) Kresse, G.; Joubert, D. From Ultrasoft Pseudopotentials to the Projector Augmented-Wave Method. *Phys. Rev. b* **1999**, *59* (3), 1758.
- (73) Perdew, J. P.; Burke, K.; Wang, Y. Generalized Gradient Approximation for the Exchange-Correlation Hole of a Many-Electron System. *Phys. Rev. B* **1996**, *54* (23), 16533.
- (74) Datta, D.; Li, J.; Shenoy, V. B. Defective Graphene as a High-Capacity Anode Material for Na- and Ca-Ion Batteries. *ACS Appl. Mater. Interfaces* **2014**, *6* (3), 1788–1795. <https://doi.org/10.1021/am404788e>.
- (75) Mukherjee, R.; Thomas, A. V.; Datta, D.; Singh, E.; Li, J.; Eksik, O.; Shenoy, V. B.; Koratkar, N. Defect-Induced Plating of Lithium Metal within Porous Graphene Networks. *Nat. Commun.* **2014**, *5*. <https://doi.org/10.1038/ncomms4710>.
- (76) Willems, T. F.; Rycroft, C. H.; Kazi, M.; Meza, J. C.; Haranczyk, M. Algorithms and Tools for High-Throughput Geometry-Based Analysis of Crystalline Porous Materials. *Microporous Mesoporous Mater.* **2012**, *149* (1), 134–141.



- (77) Ward, L.; Dunn, A.; Faghaninia, A.; Zimmermann, N. E. R.; Bajaj, S.; Wang, Q.; Montoya, J.; Chen, J.; Bystrom, K.; Dylla, M.; Chard, K.; Asta, M.; Persson, K. A.; Snyder, G. J.; Foster, I.; Jain, A. Matminer: An Open Source Toolkit for Materials Data Mining. *Comput. Mater. Sci.* **2018**, *152* (April), 60–69. <https://doi.org/10.1016/j.commatsci.2018.05.018>.
- (78) Ong, S. P.; Richards, W. D.; Jain, A.; Hautier, G.; Kocher, M.; Cholia, S.; Gunter, D.; Chevrier, V. L.; Persson, K. A.; Ceder, G. Python Materials Genomics (Pymatgen): A Robust, Open-Source Python Library for Materials Analysis. *Comput. Mater. Sci.* **2013**, *68*, 314–319.
- (79) Ong, S. P.; Cholia, S.; Jain, A.; Brafman, M.; Gunter, D.; Ceder, G.; Persson, K. A. The Materials Application Programming Interface (API): A Simple, Flexible and Efficient API for Materials Data Based on REpresentational State Transfer (REST) Principles. *Comput. Mater. Sci.* **2015**, *97*, 209–215.
- (80) Rao, C.; Liu, Y. Three-Dimensional Convolutional Neural Network (3D-CNN) for Heterogeneous Material Homogenization. *Comput. Mater. Sci.* **2020**, *184*, 109850.
- (81) Azimi, S. M.; Britz, D.; Engstler, M.; Fritz, M.; Mücklich, F. Advanced Steel Microstructural Classification by Deep Learning Methods. *Sci. Rep.* **2018**, *8* (1), 2128.
- (82) Faber, F.; Lindmaa, A.; Lilienfeld, O. A. Von; Armiento, R. Crystal Structure Representations for Machine Learning Models of Formation Energies. **2015**. <https://doi.org/10.1002/qua.24917>.
- (83) Ghiringhelli, L. M.; Vybiral, J.; Levchenko, S. V.; Draxl, C.; Scheffler, M. Big Data of Materials Science: Critical Role of the Descriptor. *Phys. Rev. Lett.* **2015**, *114* (10), 105503.
- (84) Aguiar, J. A.; Gong, M. L.; Tasdizen, T. Crystallographic Prediction from Diffraction and Chemistry Data for Higher Throughput Classification Using Machine Learning. *Comput. Mater. Sci.* **2020**, *173* (October), 109409. <https://doi.org/10.1016/j.commatsci.2019.109409>.
- (85) Gulli, A.; Pal, S. *Deep Learning with Keras*; Packt Publishing Ltd, 2017.
- (86) O'Malley, T.; Bursztein, E.; Long, J.; Chollet, F.; Jin, H.; Invernizzi, L. Keras Tuner. *Retrieved May 2019*, *21*, 2020.
- (87) Chollet, F. K. Available Online: <https://Keras.io> (Accessed on 14 August 2019). © 2019 by the Authors. *Licens. MDPI, Basel, Switzerland. This Artic. is an open access Artic. Distrib. under terms Cond. Creat. Commons Attrib. (CC BY) Licens. (http://creativecommons.org/licenses/by/4.0/)* **2015**.



- (88) Czarnecki, W. M.; Podlowska, S.; Bojarski, A. J. Robust Optimization of SVM Hyperparameters in the Classification of Bioactive Compounds. *J. Cheminform.* **2015**, *7* (1), 1–15. <https://doi.org/10.1186/s13321-015-0088-0>.
- (89) Stergiou, K.; Ntakolia, C.; Varytis, P.; Koumoulos, E.; Karlsson, P.; Moustakidis, S. Enhancing Property Prediction and Process Optimization in Building Materials through Machine Learning: A Review. *Comput. Mater. Sci.* **2023**, *220*, 112031.
- (90) Omee, S. S.; Louis, S.-Y.; Fu, N.; Wei, L.; Dey, S.; Dong, R.; Li, Q.; Hu, J. Scalable Deeper Graph Neural Networks for High-Performance Materials Property Prediction. *Patterns* **2022**, *3* (5), 100491.
- (91) Dwivedi, V. P.; Joshi, C. K.; Luu, A. T.; Laurent, T.; Bengio, Y.; Bresson, X. *Benchmarking Graph Neural Networks*; 2020.
- (92) Bader, R. F. W. Atoms in Molecules. *Acc. Chem. Res.* **1985**, *18* (1), 9–15. <https://doi.org/10.1021/ar00109a003>.
- (93) Batatia, I.; Batzner, S.; Kovács, D. P.; Musaelian, A.; Simm, G. N. C.; Drautz, R.; Ortner, C.; Kozinsky, B.; Csányi, G. The Design Space of E (3)-Equivariant Atom-Centered Interatomic Potentials. *arXiv Prepr. arXiv2205.06643* **2022**.
- (94) Hsu, T.; Pham, T. A.; Keilbart, N.; Weitzner, S.; Chapman, J.; Xiao, P.; Qiu, S. R.; Chen, X.; Wood, B. C. Efficient and Interpretable Graph Network Representation for Angle-Dependent Properties Applied to Optical Spectroscopy. *npj Comput. Mater.* **2022**, *8* (1), 151.
- (95) Morris, C.; Rattan, G.; Mutzel, P. Weisfeiler and Leman Go Sparse: Towards Scalable Higher-Order Graph Embeddings. *Adv. Neural Inf. Process. Syst.* **2020**, *33*, 21824–21840.
- (96) Maron, H.; Litany, O.; Chechik, G.; Fetaya, E. On Learning Sets of Symmetric Elements. In *International conference on machine learning*; PMLR, 2020; pp 6734–6744.
- (97) Kim, S.; Noh, J.; Gu, G. H.; Aspuru-Guzik, A.; Jung, Y. Generative Adversarial Networks for Crystal Structure Prediction. *ACS Cent. Sci.* **2020**, *6* (8), 1412–1420.

