

Magnetic structure and Kondo lattice behavior in CeVGe₃: an NMR and neutron scattering study

C. Chaffey,¹ H. C. Wu,^{2,*} Hanshang Jin,¹ P. Sherpa,¹ Peter Klavins,¹ M. Avdeev,^{3,4} S. Aji,² R. Shimodate,² K. Nawa,² T. J. Sato,² V. Taufour,¹ and N. J. Curro^{1,†}

¹*Department of Physics and Astronomy, University of California Davis, Davis, CA*

²*Institute of Multidisciplinary Research for Advanced Materials, Tohoku University, Sendai 980-8577, Japan*

³*Australian Centre for Neutron Scattering, Australian Nuclear Science and Technology Organisation, Kirrawee DC, NSW 2232, Australia*

⁴*School of Chemistry, The University of Sydney, Sydney 2006, Australia.*

(Dated: August 14, 2023)

We present nuclear magnetic resonance (NMR), neutron diffraction, magnetization, and transport measurements on a single crystal and powder of CeVGe₃. This material exhibits heavy fermion behavior at low temperature, accompanied by antiferromagnetic (AFM) order below 5.8 K. We find that the magnetic structure is incommensurate with AFM helical structure, characterized by a magnetic modulated propagation vector of (0, 0, 0.49) with in-plane moments rotating around the *c*-axis. The NMR Knight shift and spin-lattice relaxation rate reveal a coherence temperature $T^* \sim 15$ K, and the presence of significant antiferromagnetic fluctuations reminiscent of the archetypical heavy fermion compound CeRhIn₅. We further identify a metamagnetic transition above $H_m \sim 2.5$ T for magnetic fields perpendicular to *c*. We speculate that the magnetic structure in this field-induced phase consists of a superposition with both ferromagnetic and antiferromagnetic components, which is consistent with the NMR spectrum in this region of the phase diagram. Our results thus indicate that CeVGe₃ is a hexagonal structure analog to tetragonal CeRhIn₅.

I. INTRODUCTION

Heavy electron materials manifest a broad spectrum of correlated-electron phenomena, including long-range antiferromagnetism, quantum criticality, and unconventional superconductivity [1–3]. In these systems, the *f* electrons tend to be more localized, but interact weakly with itinerant conduction electrons via a Kondo interaction. This interaction can lead to long-range magnetic order via a Ruderman-Kittel-Kasuya-Yosida (RKKY) interaction between the *f* electron moments, or delocalization of the *f* electrons by hybridizing with the conduction electrons and formation of a narrow band with enhanced mass [4]. Frequently, pressure tuning uncovers a regime of non-Fermi liquid behavior that may be associated with an underlying quantum phase transition [5, 6]. Many of these materials have tetragonal lattices, such as the prototypical CeMIn₅ family with M = Co, Rh, or Ir [7–9] or the ThCr₂Si₂ structure of YbRh₂Si₂ [10, 11], CeCu₂Si₂ [12] or URu₂Si₂ [13]. Less is known, however, about the behavior of systems with other crystal symmetries.

CeVGe₃ crystallizes in the hexagonal *P*6₃/*mmc* space group with two Ce atoms per unit cell, where the structure can be viewed as sheets of Ce with AB-type stacking, as illustrated in Fig. 1 [14]. The nearest neighbor Ce-Ce distance of 4.58 Å is similar to that in the CeMIn₅ materials, hence naively one might expect to find similar Kondo lattice physics. Indeed, CeVGe₃ exhibits antiferromagnetism below $T_N = 5.5$ K [15]. In the paramagnetic

phase, the magnetic susceptibility reveals an effective moment that is close to that expected for Ce³⁺ ($2.54\mu_B$), and the heat capacity exhibits a large peak at T_N . However, the entropy reaches only $0.5R\ln 2$ at 7 K, suggesting a significant Kondo interaction. Moreover, the contribution of the 4*f* orbitals to the resistivity indicates broad peaks at 30 K and 50 K along the *a* and *c* directions, indicative of the onset of Kondo lattice coherence [16]. It is interesting to note that the hexagonal sheet structure of this material gives rise to a Dirac dispersion at the *K* points in momentum space. Kondo physics is not expected to emerge in a Dirac semimetal when the Fermi level is precisely at the Dirac point, but can be present if the Dirac point lies below [17].

Little is known about the magnetic structure in CeVGe₃. Bulk measurements of the magnetization have revealed a Curie-Weiss temperature θ_{CW} that is significantly higher than T_N , suggesting the presence of frustration [15]. On the other hand, crystalline electric field (CEF) and Kondo interactions can significantly alter the low temperature magnetic susceptibility [18]. A recent study of the magnetic response suggests that the CEF ground state in this material is Γ_6 , corresponding to $|J_z = \pm 1/2\rangle$ [19]. The measured magnetization anisotropy indicates that the easy axis lies in the basal plane, and the anisotropy agrees with the calculated *g*-factor for this state. Moreover, the first excited state doublet lies at $\Delta = 137$ K, well above the Kondo lattice coherence temperature. In-plane field-dependent measurements revealed a temperature-dependent metamagnetic transition around 2.5 T [15]. NMR studies of polycrystals of CeTi_{1-x}V_xGe₃ uncovered a competition between ferromagnetic and antiferromagnetic spin fluctuations in the vicinity of a ferromagnetic quantum critical

* wu.hung.cheng.d2@tohoku.ac.jp

† njcurro@ucdavis.edu

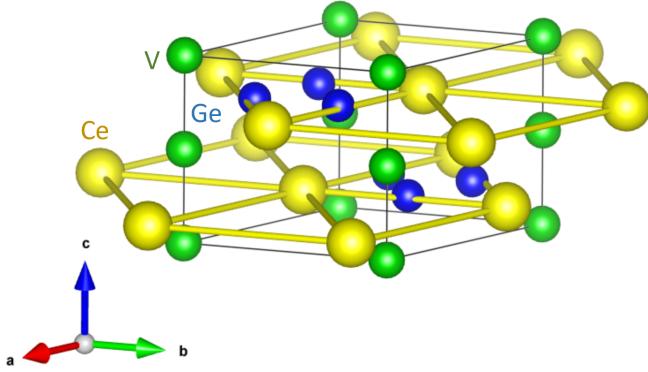


FIG. 1. Hexagonal crystal structure of CeVGe_3 , with Ce in yellow, V in green, and Ge in blue.

point [20, 21].

In order to better understand the nature of the long-range order in this material, we have conducted detailed nuclear magnetic resonance (NMR), neutron scattering studies, and transport measurements on a single crystal and powder of CeVGe_3 . Our results reveal a helical structure in zero field, in which the Ce moments lie in the basal plane and rotate along the c -axis. In-plane fields destabilize this structure, suppressing T_N and giving rise to a first-order metamagnetic transition for fields $\gtrsim 2.5$ T. The NMR spectra in this field-induced phase are consistent with a structure with partial polarization along the applied field and commensurate antiferromagnetism along the c -axis. In the paramagnetic phase, the NMR Knight shift reveals anomalous behavior below a coherence temperature $T^* \sim 15$ K, consistent with the onset of Kondo lattice behavior, and the spin lattice relaxation rate indicates significant antiferromagnetic fluctuations. These results indicate that although it has a hexagonal rather than a tetragonal lattice structure, CeVGe_3 exhibits behavior analogous to the archetypical heavy fermion CeRhIn_5 .

II. KONDO PHYSICS

A. NMR Knight Shift

A single crystal of CeVGe_3 with dimensions $5 \times 2 \times 2$ mm³ was secured in an NMR coil placed in an external field of 11.7 T. Spectra were acquired for fields both parallel and perpendicular to the c -axis by sweeping frequency as a function of temperature, as shown in Fig. 2. There is a single V site per unit cell, located centrosymmetrically between the Ce sheets. Because ${}^{51}\text{V}$ is spin $I = 7/2$, there are seven transitions at frequencies given by $\nu_n = \gamma H_0(1 + K) + n\nu_q$, where $\gamma = 11.193$ MHz/T is the gyromagnetic ratio, K is the magnetic shift, $n = -3, \dots, +3$, and ν_q is the quadrupolar shift that arises due to the electric field gradient (EFG) tensor. The crystal has axial symmetry, hence the EFG

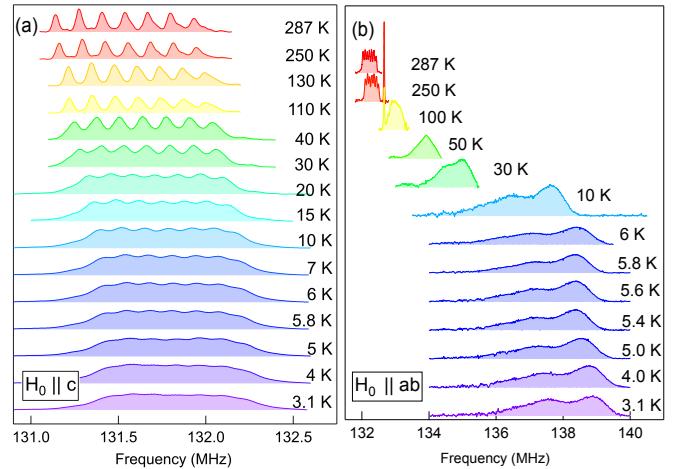


FIG. 2. ${}^{51}\text{V}$ NMR spectra for (a) $\mathbf{H}_0 \parallel [001]$ and (b) $\mathbf{H}_0 \perp [001]$ as a function of temperature in an external field of 11.7285 T.

tensor can be fully represented by a single quantity, $\nu_{zz} = (eQ/84h)\partial^2V/\partial z_\alpha^2$, where $Q = 5.2 \times 10^{-30}\text{m}^2$ is the quadrupolar moment of the ${}^{51}\text{V}$, and the quadrupolar shift $\nu_q = \nu_{zz}(3\cos^2\theta - 1)/2$ where θ is the angle between \mathbf{H}_0 and the c -axis. The spectra were fit to a sum of Gaussians or Lorentzians to extract K , ν_{zz} and linewidths, as shown in Figs. 3(a,b) and 4. In both cases, the spectra shift upwards in frequency with decreasing temperature, and the quadrupolar splitting between the peaks remains temperature independent. This behavior agrees with previous observations in polycrystalline samples [21]. For $\mathbf{H} \perp c$, the spectra broaden by an order of magnitude below ~ 105 K, such that the quadrupolar splitting gets washed out. Upon further cooling, the spectra exhibit two broad peaks. The origin of these peaks and their shape is discussed below in section III.C. The shifts of these two peaks are labelled K_{ab} (high/low) and shown in Fig. 4. The strong temperature dependence of the shift and the broadening, accompanied by the lack of any change in the EFG, reflect properties of the magnetism, rather than any inhomogeneous broadening due to a distribution of local EFGs.

The temperature dependence of the Knight shift tracks the bulk susceptibility for temperatures $T \gtrsim 30$ K. This behavior arises due to the hyperfine coupling between the nuclear and electron spins: $\mathcal{H}_{hyp} = \hat{\mathbf{I}} \cdot \mathbb{A} \cdot \mathbf{S}_c + \hat{\mathbf{I}} \cdot \mathbb{B} \cdot \mathbf{S}_f$, where $\mathbf{S}_{c,f}$ correspond to the conduction or f -electron spins, and \mathbb{A} and \mathbb{B} correspond to the hyperfine tensors to these two spin species. The Knight shift and bulk susceptibility are given by [22–24]:

$$K = A\chi_{cc} + (A + B)\chi_{cf} + B\chi_{ff} \quad (1)$$

$$\chi = \chi_{cc} + 2\chi_{cf} + \chi_{ff} \quad (2)$$

where $\chi_{ij} = \langle S_i S_j \rangle$ and $(i, j) = (c, f)$. For sufficiently high temperatures, the local moment susceptibility dominates, and $\chi \approx \chi_{ff}$. In this case $K = K_0 + B\chi$, and the transferred hyperfine coupling to the local moments

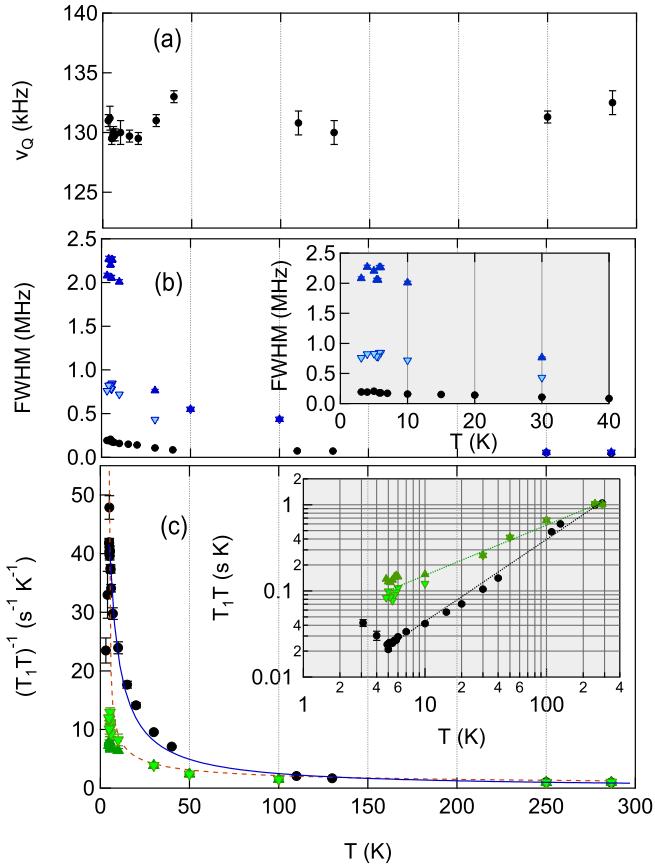


FIG. 3. (a) Electric field gradient, ν_Q , versus temperature. (b) Linewidth versus temperature for $\mathbf{H}_0 \parallel c$ (●) and $\mathbf{H}_0 \perp c$ (▽, ▲). The inset focuses on the low temperature behavior. (c) $(T_1 T)^{-1}$ versus temperature (same symbols as for (b)). The solid line is a fit to a Curie-Weiss form, and the dashed line is a fit to the SCR expression, as discussed in the text. INSET: $T_1 T$ versus temperature for both field directions. The dotted lines are fits to a power law with exponent 0.95 ± 0.01 for $\mathbf{H}_0 \parallel c$ and 0.58 ± 0.03 for $\mathbf{H}_0 \perp c$.

is given by the slope in a plot of K versus $\chi = M/H$, as shown in the inset of Fig. 4. We find that $B_{\parallel} = 0.4 \pm 0.1$ kOe/ μ_B and $B_{\perp} = 1.3 \pm 0.2$ kOe/ μ_B , and that $K_{0,\parallel} = 0.18 \pm 0.01\%$ and $K_{0,\perp} = 0.40 \pm 0.06\%$. These values agree well with the isotropic hyperfine coupling reported in polycrystalline samples [21].

These couplings presumably arise due to the overlap of the wavefunction of the Ce $4f$ and V $3d$ and $4s$ orbitals. In the CeMIn₅ system, the transferred hyperfine couplings are determined by the hybridization between the CEF ground state of the $4f$ wavefunction and the neighboring ligand sites [25]. Recently, a study of the magnetic properties of CeVGe₃ [19] indicated that the ground state of the $4f$ is the Γ_6 manifold, with $|J_z = \pm 1/2\rangle$, in contrast to the CeMIn₅ system [26]. In this case, the $4f$ orbital is extended spatially along the c -axis, and may have a small overlap with the V site. This fact may explain why the transferred hyperfine coupling in CeVGe₃ is much smaller than in CeRhIn₅, despite the fact that

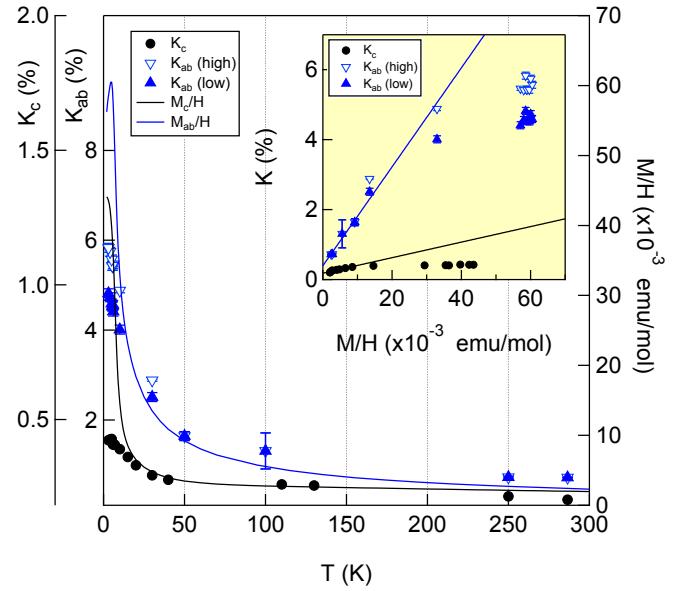


FIG. 4. Knight shifts, K_c (●) and K_{ab} (▽, ▲) as a function of temperature compared with the bulk susceptibility, M/H (solid lines), measured at 1 T. INSET: The Knight shift versus bulk susceptibility for both directions. The solid lines are fits as described in the text.

the gyromagnetic ratio of ^{51}V and ^{115}In are similar in magnitude [22, 27]. Further studies of the hyperfine coupling in the Ce(V,Ti)Ge₃ may reveal dramatic changes, as the ground state wavefunction is expected to change from Γ_6 to Γ_7 as a function of Ti doping [19].

Below $T \approx 20$ K, the Knight shift deviates from the bulk susceptibility, as shown in Fig. 4. This behavior reflects the increase of χ_{cf} below the Kondo lattice coherence scale [24, 28]. In this case, we can construct the quantity $K_{cf} = K - B\chi \propto \chi_{cf} + \chi_{cc}$, which quantifies the growth of the heavy electrons. This quantity is shown in Fig. 5 for both directions. The data exhibit similar behavior for $T \gtrsim 5$ K. The temperature dependence is expected to be described by:

$$K_{cf}(T) = K_{cf}^0 (1 - T/T^*)^{3/2} [1 + \log(T^*/T)] \quad (3)$$

where T^* is the coherence temperature and K_{cf}^0 is a temperature independent constant that depends on the undetermined on-site hyperfine coupling A [29]. The solid line in Fig. 5 is a fit to this expression for $T > 5$ K, which yields $T^* = 15 \pm 1$ K. Below 5 K, this scaling breaks down such that K_{cf} is less than the expected value in both directions. In fact, K_{cf} actually decreases for the perpendicular direction. Similar behavior, known as relocalization, has been observed in other heavy electron antiferromagnets, including CeRhIn₅ [23] and CePt₂In₇ [30]. In this case, the physical picture is that the growth of the heavy electron fluid is interrupted by the growth of critical antiferromagnetic correlations as the temperature decreases towards T_N . This phenomenon may also be related to the effect of the large NMR field on the Kondo

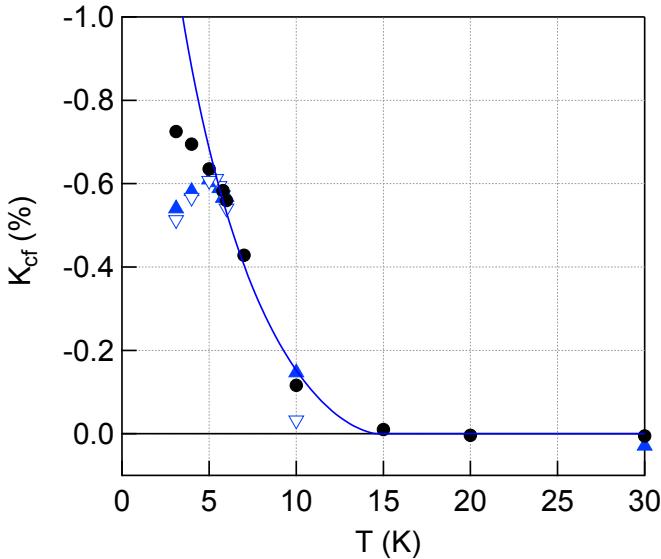


FIG. 5. K_{cf} versus temperature for $\mathbf{H}_0 \parallel c$ (●) and $\mathbf{H}_0 \perp c$ (▽, ▲). The solid line is a fit as described in the text. For the high (low) shift in the perpendicular direction, the data have been scaled by a factor of 0.14 (0.18).

physics, as the Kondo temperature $T_K \sim 10\text{K}$ [20].

B. Spin Lattice Relaxation Rate

The spin lattice relaxation rate, T_1^{-1} , was measured by inversion recovery at the central transition ($I_z = +1/2 \leftrightarrow -1/2$). The magnetization recovery was fit to the standard expression for a spin 7/2 nucleus: $M(t) = M_0 (1 - 2f \sum_n A_n e^{-\alpha_n t/T_1})$ where M_0 is the equilibrium nuclear magnetization, f is the inversion fraction, $A_1 = 1225/1716$, $A_2 = 75/364$, $A_3 = 3/44$, $A_4 = 1/84$, $\alpha_1 = 28$, $\alpha_2 = 15$, $\alpha_3 = 6$, and $\alpha_4 = 1$. There was no evidence of any stretched relaxation, or any signal wipeout. For $\mathbf{H}_0 \perp c$, T_1^{-1} was measured at both broad peaks at low temperatures where the quadrupolar splitting was no longer resolved. The temperature dependence of $(T_1 T)^{-1}$ is shown in Fig. 3(c). For both directions this quantity diverges strongly with reduced temperature, and exhibits a peak at 5 K. This value is reduced relative to bulk measurements in zero field, suggesting that T_N is suppressed by in-plane magnetic fields. This observation is confirmed by magnetization measurements, as discussed below.

The spin lattice relaxation rate probes the dynamical part of the spin susceptibility through the relation:

$$\left(\frac{1}{T_1 T} \right)_\alpha = \gamma^2 k_B \lim_{\omega \rightarrow 0} \sum_{\mathbf{q}, \beta \neq \alpha} \mathcal{F}_{\alpha\beta}(\mathbf{q}) \frac{\text{Im} \chi_{\alpha\beta}(\mathbf{q}, \omega)}{\hbar \omega}, \quad (4)$$

where $\mathcal{F}_{\alpha\beta}(\mathbf{q})$ are form factors that depend on the hyperfine coupling tensor, $\chi_{\alpha\beta}(\mathbf{q}, \omega)$ is the dynamical magnetic susceptibility, and $\alpha, \beta = \{x, y, z\}$ [31]. The large peak in

$(T_1 T)^{-1}$ reflects the slowing down of critical fluctuations near T_N .

According to the self-consistent renormalized (SCR) theory of spin fluctuations for weak itinerant antiferromagnets $(T_1 T)^{-1} \propto \chi_Q(T)^n$, where $n = 1/2$ for 3D fluctuations and $n = 1$ for 2D fluctuations [32]. The dotted and solid lines in Fig. 3(c) are fits to $n = 1/2$ and $n = 1$ with $\chi_Q(T) = C/(T + \theta_{\text{CW}})$, where $\theta_{\text{CW}} = -4.8 \pm 0.1\text{ K}$ for $n = 1/2$, and $\theta_{\text{CW}} = 1.0 \pm 0.1\text{ K}$ for $n = 1$. The solid line provides a much better fit to the data for $\mathbf{H}_0 \parallel c$, suggesting that the fluctuations are predominantly 2D in nature for this direction. The inset of Fig. 3(c) shows $T_1 T$ versus temperature for both directions, as well as power law fits. For the parallel direction, the best fit yields an exponent $n = 0.95 \pm 0.01$, but for the perpendicular direction, the best fit yields $n = 0.59 \pm 0.03$. This result suggests that for the perpendicular field, the fluctuations exhibit 3D character in contrast to the parallel direction. This behavior may be related to the presence of a different magnetic structure above the metamagnetic transition in the perpendicular direction, as discussed below. The related heavy fermion antiferromagnet CeRhIn₅ exhibits more 3D spin fluctuations [27, 33]. On the other hand, $(T_1 T)^{-1}$ in the heavy fermion superconductor CeCoIn₅ exhibits an unusual $T^{1/4}$ behavior that has been associated with proximity to an antiferromagnetic quantum critical point [34]. The superconductor CeIrIn₅ exhibits behavior that is in some sense a hybrid between 2D and 3D, with $(T + \theta)^{3/4}$ that has been associated with the layered structure [35]. The values in Fig. 3(c) are similar in magnitude to those reported in polycrystals of CeVGe₃ [21]. In that case, the behavior also did not agree with the SCR form, and it was suggested that ferromagnetic fluctuations may also be present.

III. MAGNETIC ORDERING

A. Neutron Scattering

The Kondo effect can cause a reduction in the magnetic moment of a material. To investigate the size of the ordered moment in CeVGe₃, neutron powder diffraction experiments were conducted below and above T_N . Figure 6(a) displays the neutron powder diffraction pattern obtained at 12 K (above T_N), along with the corresponding Rietveld refinement. The refined parameter and reliable factors are summarized in Table I. The result indicates that the crystal structure at 12 K is the same as that investigated at room temperature [19], which is depicted in Fig. 1. Additionally, Fig. 6(b) provides an enlarged view of the low-angle region, measured at temperatures of 3.0 K and 12 K. The difference pattern reveals the emergence of two distinct magnetic scattering intensities at positions $|\mathbf{Q}_1|$ and $|\mathbf{Q}_2|$. It is not possible to index these reflections with rational numbers, suggesting the presence of a potential incommensurate magnetic ground

state in CeVGe_3 . Assuming that $|\mathbf{Q}_1|$ occurs along the high symmetry direction, the magnetic propagation vector (\vec{k}) can be indexed as $(0.46, 0, 0)$ or $(0.33, 0.33, 0)$ in the basal plane (in units of the reciprocal lattice vectors). If $|\mathbf{Q}_1|$ aligns with the c axis, the estimated \vec{k} value would be approximately $(0, 0, 0.48)$.

To determine the exact \vec{k} , single crystal neutron diffraction was performed with the crystal aligned with the $HK0$ plane as the scattering plane. One-dimensional (1D) reciprocal-space scans along $(H, 0, 0)$, $(-H, H, 0)$ and $(H, H, 0)$ at base temperature 2.7 K did not reveal any magnetic reflection. Additionally, a two-dimensional (2D) reciprocal-space mesh scan at 2.7 K was conducted to detect satellite magnetic reflections, where $H \neq K$ in the basal plane. However, no additional scattering intensity was observed (Fig. 11 in Appendix C), strongly suggesting that \vec{k} does not predominantly lie within the basal plane. Alternatively, magnetic reflections may be present in regions outside of the basal plane.

The single crystal was then rotated by 90 degrees from the $HK0$ plane to the HHL plane as the new scattering plane. The 1D reciprocal-space scans along the $(0, 0, L)$ and $(1, 1, L)$ directions at 2.7 K and 6.0 K were plotted and shown in Fig. 7(a,b). No magnetic reflections were observed on the top of the nuclear or forbidden nuclear positions in the HHL plane. On the other hand, satellite magnetic reflections were observed between these nuclear peaks. Figures 7(c,d) display an enlarged view of the selected magnetic reflections at 2.7 K and 6.0 K. Their peak positions were determined to be $(0, 0, 0.49)$ and $(0, 0, 1.51)$. Figure 7(e) illustrates the distribution of squared magnetic structure factors in HHL plane. In this case, satellite magnetic reflections (Fig. 7(e)) were successfully observed at positions $(0, 0, 0.49)$, $(0, 0, 1.51)$, $(0, 0, 2.49)$, $(1, 1, 0.49)$, $(1, 1, 1.51)$, and $(1, 1, 2.49)$. It should be noted that other than the allowed nuclear reflections, some peaks were present along $(0, 0, L)$ and $(1, 1, L)$ directions. All of them are temperature independent and are not intrinsic. The reflections at $(0, 0, 1)$, $(0, 0, 3)$, and $(1, 1, 1)$ are likely due to the higher-harmonic contributions, while those at $(0, 0, 2.26)$ and $(1, 1, 2.13)$ are from the Al sample holder. We also find some intensity at $(0, 0, 0.655)$, $(0, 0, 1.33)$, and $(0, 0, 2.665)$, which could arise from an unknown impurity phase included in the crystal. None of these reflections affect the analysis discussed below.

Based on the data from the $HK0$ and the HHL planes, we conclude that the ground state exhibits a single- k incommensurate magnetic (ICM) structure with $\vec{k} = (0, 0, 0.49)$. The temperature dependence of the integrated intensity of the most intense magnetic reflection $(0, 0, 0.49)$ is depicted in Fig. 7(f). From the fit to the power-law function with a constant background, we estimate $T_N = 5.80(16)$ K, which is consistent with the magnetization measurements [15, 19].

To analyze incommensurate magnetic (ICM) structures, we employed the magnetic representation method.

The allowed irreducible representations (IRs) for the Ce ($2d$) site within the $P6_3/mmc$ space group with $k = (0, 0, 0.49)$ are summarized in Table II in Appendix C. Examination of the basis vectors associated with each IR reveals that IR2 and IR5 are 1D IRs, while IR3 and IR6 belong to 2D IRs. Models based on IR2 and IR5 were discarded because they resulted in allowed magnetic structures where the Ce layers align ferromagnetically along c axis and stack antiferromagnetically. These results are inconsistent with the magnetization data [15, 19]. Additionally, it was observed that the simulated magnetic intensities did not align well with the observed intensities. For instance, magnetic reflections along the $00L$ direction were not expected due to the polarization factor. On the other hand, IR3 and IR6 correspond to in-plane helical structures. In the case of IR3, the calculated magnetic structure factor at $(0, 0, 0.49)$ is zero, while the most intense magnetic structure factor appears at $(0, 0, 0.51)$. These results are in direct contradiction with the experimental observations. Only IR6 reproduces the positions and the intensities of the observed magnetic reflections.

The magnetic structure factors obtained from the single crystal data measured at 2.7 K were utilized for a least-square refinement employing the IR6 model. To simplify the refinement process and reduce the number of parameters, the atomic position and lattice constants were fixed to those obtained from powder diffraction at 12 K. In addition, a simplifying assumption was made that the moment size of all Ce atoms is the same. This reduces the number of refinement parameters from two to one, corresponding to the moment size. The helical structure with a fixed moment size is represented by a single BV, where BV1 represents a counter-clockwise rotating helical structure and BV2 represents a clockwise helical structure. Since they could not be distinguished through refinement, the coefficient of BV1 was used as an adjustable parameter. The calculated and observed magnetic structure factors were compared in Fig. 8(a). A scale factor was determined from the 110 nuclear reflection. Despite having only a single adjustable parameter, the six observed magnetic reflections were well reproduced. The estimated moment size at 2.7 K was $0.49(1)$ μ_B .

The magnetic structure was further confirmed through neutron powder diffraction, as shown in Fig. 6(c). The peak at $|\mathbf{Q}_1|$ was indexed as $0\ 0\ 0.49$, while the peak at $|\mathbf{Q}_2|$ was a superposition of $1\ 0\ 0.49$ and $1\ 0\ 0.51$ reflections. A moment size of $0.38(1)$ μ_B at 3.0 K was estimated from the Rietveld refinements using the difference pattern. The red circles in Fig. 6(c) represent the helical structure with a fixed moment size, and accurately reproduce the intensity of the two peaks. The estimated moment sizes from both data sets are very close, with any small differences likely attributable to the slight variation in sample temperature.

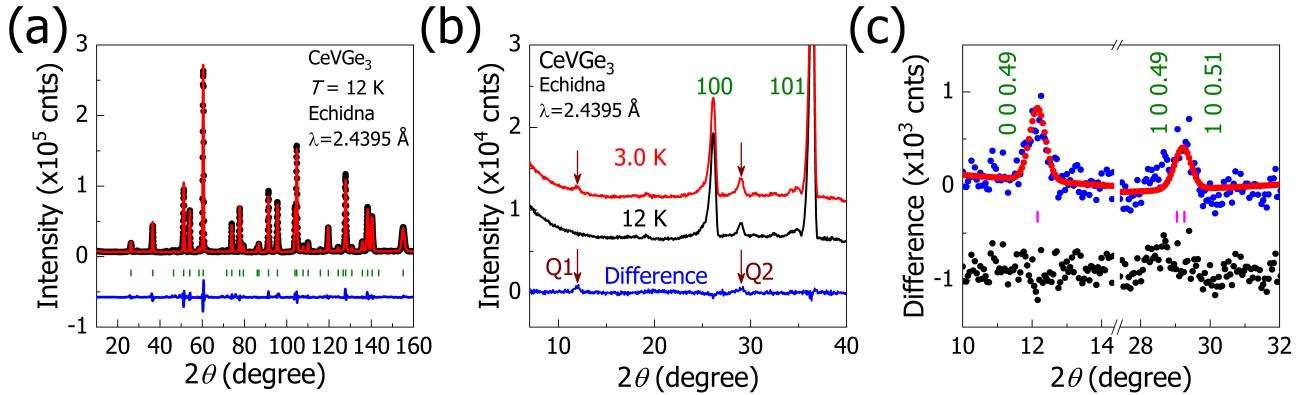


FIG. 6. (a) Neutron powder diffraction pattern (black circles) at 12 K, along with the corresponding Rietveld refinement (red line). The green bar represents the allowed positions of nuclear reflections. The negligible difference pattern (blue line) between the nuclear contribution and the refined pattern confirms the accuracy and reliability of the crystal structure model. (b) Neutron powder diffraction pattern at 3.0 K (red line) and 12 K (black line), respectively, offset for clarity. The difference pattern (blue line) indicates the presence of magnetic reflections, as indicated by the arrows. (c) The difference pattern (blue circles) between 3.0 K and 12 K, along with the simulated pattern of in-plane helical magnetic structure (red circles). The pink bars indicate the allowed magnetic reflection positions. The negligible difference (black circles) between the observed magnetic contribution and the simulated pattern confirms the validity of the estimated moment size.

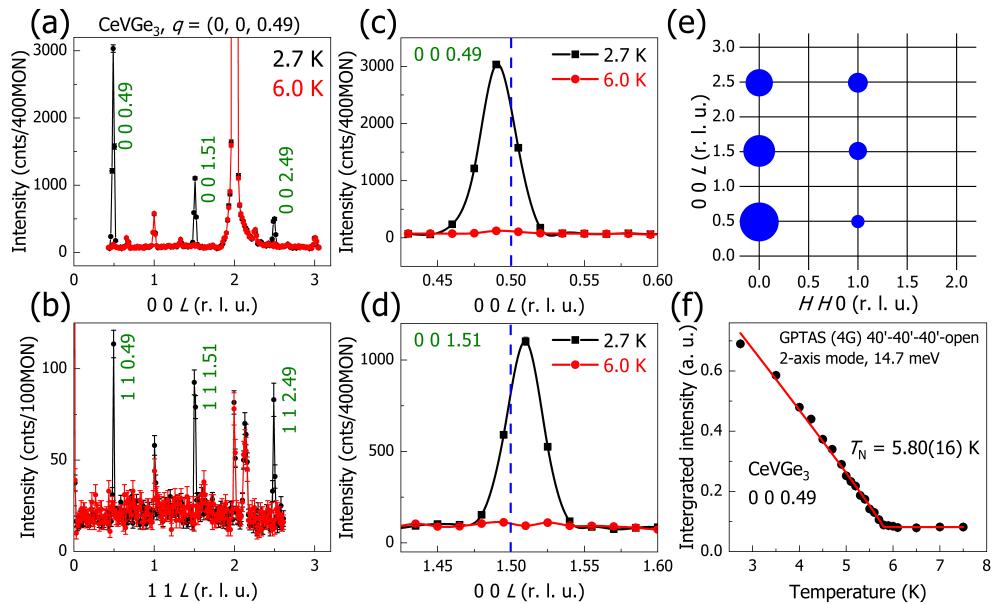


FIG. 7. The raw dataset of the reciprocal space L -scan along the (a) $(0,0,L)$ and (b) $(1,1,L)$ direction at 2.7 K and 6.0 K. The selected reciprocal space L -scan along the $(0,0,L)$ direction with an enlarged view at (c) $(0,0,0.49)$ and (d) $(0,0,1.51)$. The blue dashed lines indicate the locations at $(0,0,0.5)$ and $(0,0,1.5)$, respectively. (e) The distribution of the squared magnetic structure factor at 2.7 K (below T_N) in the HHL plane strongly suggests that magnetic moment lies in the basal plane. (f) The temperature dependence of the integrated intensity of the $0 0 0.49$ magnetic reflection. The magnetic transition temperature is estimated to be $5.80(16) \text{ K}$.

B. Hyperfine Field

In the magnetically ordered state, the NMR resonance will be affected by a static hyperfine field given by: $\mathbf{H}_{hf} = \sum_{i=1}^6 \mathbb{B}_i \cdot \mathbf{m}(\mathbf{r}_i)$, where the \mathbb{B}_i are the transferred hyperfine couplings to the 6 n.n. Ce sites,

as discussed in Appendix B. For a helical structure of the Ce ordered moments with wavevector Q_z , the internal field rotates in the ab plane with constant magnitude, as illustrated in Fig. 9(a), and is given by $H_{hf} = 6B_{\perp}m_0 |\cos(2\pi k_z z_0/2c)|$, where $z_0 = c/2$ is the spacing between the Ce layers. Using the measured hy-

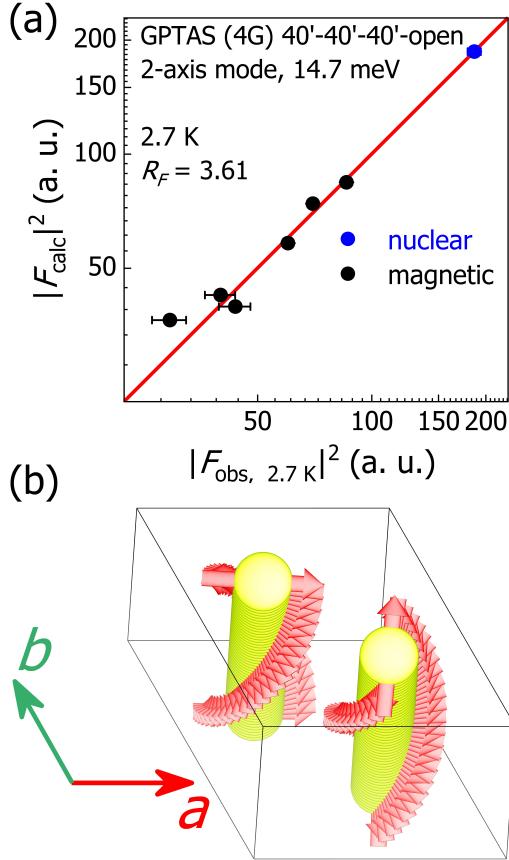


FIG. 8. (a) The calculated magnetic structure factor from the refinement versus the observed magnetic structure factor obtained at 2.7 K. (b) The proposed in-plane helical magnetic structure at zero-field obtained through refinement. The yellow circles are the two Ce sites per unit cell in adjacent layers, and the red arrows indicate the magnetic moments.

perfine couplings, and the neutron results $m_0 = 0.38\mu_B$ and $k_z = 0.49$, we estimate $H_{hf} = 0.21$ T.

In the presence of an external field, \mathbf{H}_0 , the NMR resonance frequency is given by $f = \gamma |\mathbf{H}_0 + \mathbf{H}_{hf}|$. If $\mathbf{H}_0 \parallel c$, then the resonance frequency in the ordered state is given by $f = \gamma (H_0^2 + H_{hf}^2)^{1/2}$, and is homogeneous. For the applied field of 11.7 T, the resonance is shifted upwards by only 22 kHz. As seen in Fig. 2(a) and 3(b), the spectrum for $\mathbf{H}_0 \parallel c$ changes little through T_N , but already has a linewidth of ~ 200 kHz. It is likely that inhomogeneous demagnetization fields broaden the resonance sufficiently that the subtle shift due to the hyperfine field is washed out [36]. Thus the NMR response for this direction is consistent with the neutron scattering results.

C. Metamagnetic Transition

Previous work uncovered a metamagnetic transition for fields perpendicular to the c -axis [15]. Helical magnetic order is known to be unstable to the presence of

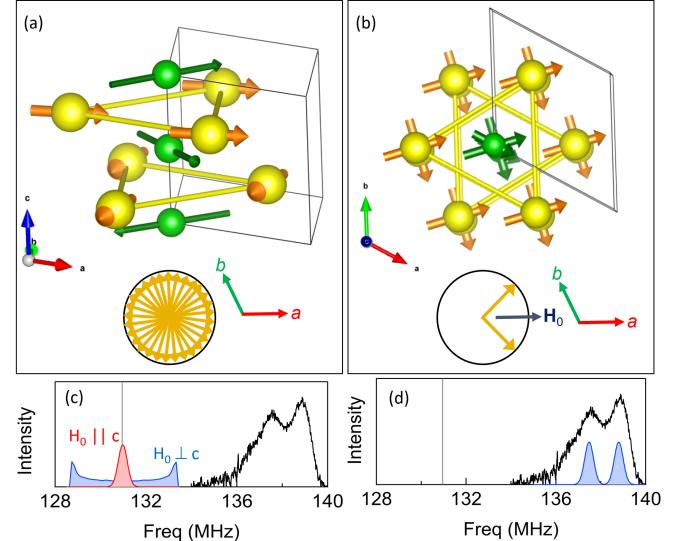


FIG. 9. (a) Magnetic structure and hyperfine fields in the low-field helicoidal phase. Orange arrows indicate ordered moments on Ce sites (yellow), and green arrows indicate hyperfine field at the V sites (green). The lower illustration indicates the projection of the Ce moments in the ab plane. (b) Magnetic structure and hyperfine fields in the field-induced phase. The external field here is directed along the crystalline a -axis, indicated by the red arrow. The lower illustration indicates the projection of the Ce moments in the ab plane relative to an in-plane field, \mathbf{H}_0 . (c) Simulated NMR spectra for the spiral structure shown in (a) for $\mathbf{H}_0 \parallel c$ and $\mathbf{H}_0 \perp c$, compared with the 3.1 K data. (d) Simulated NMR spectra for the spin-flop structure shown in (b), compared with 3.1 K data. The vertical line in (c,d) corresponds to the frequency in the absence of any hyperfine fields.

an in-plane field [37], and has been observed in CeRhIn_5 [38–40]. To determine the magnetic phase diagram of CeVGe_3 , we carried out resistivity measurements up to 14 T and magnetization measurements up to 7 T with the field applied perpendicular to the c -axis as shown in Fig. 10.

The temperature-dependent resistivity at zero field shows a sharp upturn near T_N (Fig. 10(a)), possibly due to the fact that the incommensurate helical order is accompanied by Fermi surface nesting. The peak positions of the derivative of resistivity are marked by red triangles to track the field dependence of T_N . As shown in Fig. 10(b), T_N is monotonically suppressed with increasing field. As can be seen in Fig. 10(a), the resistivity at 2 K is decreasing with increasing field, indicating that the magnetic scattering due to the helical order starts to be suppressed above 3 T.

As shown in Fig. 10(c), the anomaly corresponding to the antiferromagnetic transition in the temperature dependence of the magnetization changes: the maximum (labeled as blue diamonds) slightly increases with the field below 1 T, and is then suppressed near 2.5 T. Above 3 T, there is no obvious anomaly above 2 K.

The spin-flop transition is also detected as a field-

induced jump in magnetization with some hysteresis, as shown in Fig. 10(d). The magnetic structure above the spin-flop transition has yet to be determined, so we generally label it as another spin-density wave due to the possible nesting observed in resistivity. The phase diagram for in-plane fields is thus summarized in Fig. 10(e).

In the helical phase at zero field, the angle between the Ce moments in adjacent planes is 88.2° . This value is close to 90° , so is likely that the most stable structure in the high field SDW phase is commensurate [37]. In this case, the moments remain in the basal plane, with partial polarization along \mathbf{H}_0 (e.g. $\mathbf{m}(\mathbf{r}) = m_0 \{ \cos \alpha, \sin \alpha \cos(\pi z/c - \pi/4), 0 \}$ for field along [100]). This $++--$ structure corresponds to an up-up-down-down sequence of magnetic moments when moving along the c -axis. This arrangement of the proposed magnetic structure can be further interpreted as a composite of two magnetic components, where the superposition results in a ferromagnetic (FM) component with $\vec{k} = \{0, 0, 0\}$ and an antiferromagnetic (AFM) component with $\vec{k} = \{0, 0, 0.5\}$. Here α characterizes the angle between the moments and \mathbf{H}_0 , and for sufficiently high fields $\alpha \rightarrow 0$ corresponds to a fully polarized state. A similar structure was found in CeRhIn₅ [39], however CeRhIn₅ also exhibits a third phase with an incommensurate structure just below T_N . We find no evidence for such a region in the phase diagram of CeVGe₃.

The NMR measurements for $\mathbf{H}_0 \perp c$ were carried out at 11.7 T in the metamagnetic phase. The spectra are clearly inconsistent with a helical magnetic structure, which would generate a broad double-peaked spectrum centered at the Larmor frequency with two “horns” at $\pm \gamma H_{hf} \approx 3.7$ MHz, as illustrated in Fig. 9(c) in blue. Rather the spectrum is shifted well above the Larmor frequency, indicated by the vertical gray line.

On the other hand, our observations are consistent with the proposed $++--$ structure, as illustrated in Fig. 9(b). In this case, the hyperfine field has two possible values, depending upon whether the V site lies between Ce layers with the same spin directions ($++$ or $--$, case A) or with alternating directions ($+-$ or $-+$, case B):

$$\mathbf{H}_{hf} = \begin{cases} \pm 6B_\perp m_0 \{ \cos \alpha, \sin \alpha, 0 \} & \text{case A} \\ 6B_\perp m_0 \{ \cos \alpha, 0, 0 \} & \text{case B} \end{cases} . \quad (5)$$

This scenario thus offers a natural explanation for the presence of the upper and lower sites in the NMR spectra shown in Fig. 2(b). The frequency shift for the two cases are: $\Delta f_A = \sqrt{f_0^2 + (6\gamma B_\perp m_0)^2 + 12\gamma f_0 B_\perp m_0 \cos \alpha} - f_0$ and $\Delta f_B = 6\gamma B_\perp m_0 \cos \alpha$, where $f_0 = \gamma H_0$. These equations can be inverted to extract m_0 and α . At the lowest temperatures, we find $m_0 = 2.3\mu_B$ and $\alpha = 72^\circ$ in an applied field of 11.7 T. The resulting spectrum is illustrated in Fig. 9(d). Note that this value of m_0 is larger than that expected for a Γ_6 ground state ($1.3\mu_B$) [19]. It is possible that this result could be modified by mixing of excited crystal field levels by the applied field, however. The strong enhancement of the susceptibility and Knight

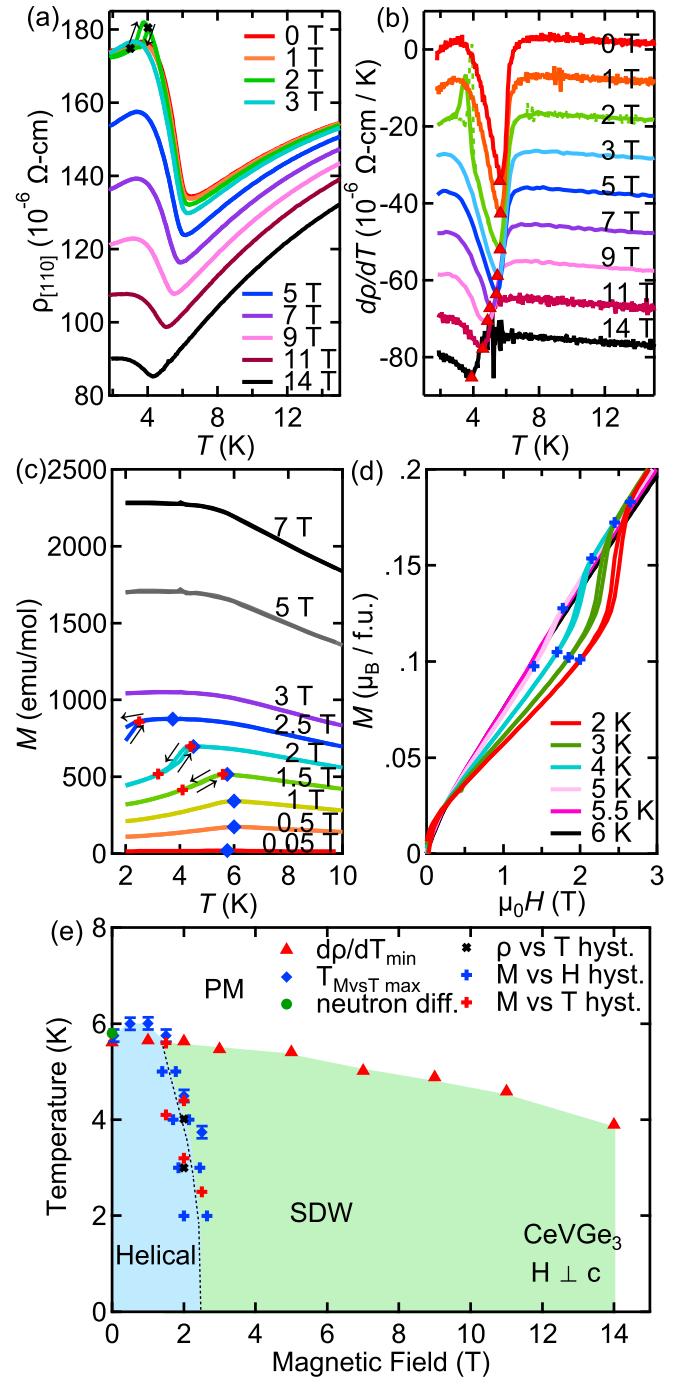


FIG. 10. (a) Temperature dependence of the in-plane resistivity $\rho(T)$ of a CeVGe₃ single crystal under various field up to 14 T. (b) Evolution of the temperature derivative of the resistivity at the low temperature under different fields. The data are vertically offset by $10 \mu\Omega \text{ cm K}^{-1}$ to reduce overlap. (c) Temperature dependence and (d) magnetic field dependence of in-plane magnetization of CeVGe₃. (e) $H - T$ phase diagram of CeVGe₃ with in-plane applied fields. The criteria to map out the phase diagram are marked in (a)-(d). Two symbols mark the beginning and end of the hysteresis.

shift in this field direction with decreasing temperature seen in Fig. 4 reflects the partial polarization of the Ce spins prior to the onset of long-range order below T_N , as captured by the angle α .

IV. DISCUSSION

Helical magnetic structures generally arise in layered structures with frustrated in-plane and out-of-plane interactions [37]. For example, in a model with ferromagnetic in-plane interaction, $J_0 < 0$, as well as both J_1 between nearest-neighbor layers, and J_2 between next-nearest-neighbor layers, the ground state magnetic structure is an incommensurate spiral with wavevector $k_z = \cos^{-1}(-J_1/4J_2)/\pi$. We therefore find $|J_1/J_2| \approx 0.13$ for CeVGe₃, with $J_1 > 0$ and $J_2 < 0$. Moreover, the metamagnetic field H_m should be related to J_2 as $H_m \approx 1.8J_2/\mu_B$, suggesting that $J_2 \sim -1$ K [37]. On the other hand, the same model predicts that the spins would be fully polarized at $\approx 2H_m \sim 5$ T, but we find no evidence of any other phase transition up to 14 T. Of course, the magnetic interactions in Ce-based heavy fermion is more complex than this simple model. Spatially-varying couplings that can give rise to spiral order can arise naturally via the RKKY interaction, but depend on the details of the Fermi surface and the Kondo interaction [41].

As seen in Fig. 2, the spectra for $\mathbf{H}_0 \perp c$ reveal two separate peaks emerging below $T \approx 30$ K, well above T_N . This is surprising because in principle the system remains paramagnetic. The origin of the two peaks in this phase remains unclear, but potentially could be related to a distribution of demagnetization fields [36]. The low frequency tail for each peak in the ordered phase is also likely related to a distribution of demagnetization fields.

As a heavy fermion compound that exhibits Kondo lattice coherence and helical antiferromagnetic order at ambient pressure, CeVGe₃ exhibits similarities to the archetypical heavy fermion system, CeRhIn₅. On the other hand, there are important differences: CeVGe₃ has hexagonal rather than tetragonal structure, the ratio of the excited state doublet energy to the Kondo coherence scale, Δ/T^* , is approximately 9.0 in CeVGe₃ versus 4.5 in CeRhIn₅ [23], and the CEF ground state manifold may be Γ_6 rather than Γ_7 . The orbitals of the latter are extended more in the plane, whereas those of the latter lie more along the c -axis [42]. The spatial form of these Ce orbitals can play a significant role in the anisotropic Kondo interactions, and may give rise to the different properties of the CeMIn₅ series as M changes due to slight alterations in the CEF interactions [26, 43]. It would therefore be of interest to examine how the ground state of CeVGe₃ evolves both as a function of doping and hydrostatic pressure. CeRhIn₅ becomes superconducting under approximately 2 GPa. It would also be valuable to examine the phase diagram of CeVGe₃ at high magnetic fields. It is also important to investigate the field depen-

dence of T_N to higher fields in CeVGe₃. A recent specific heat study up to 36 T in CeRhIn₅ identified a new field-induced phase for fields along the c -axis, possibly to a new incommensurate phase [40].

ACKNOWLEDGMENTS

Work at UC Davis was supported by the NSF under Grant No. DMR-2210613, as well as the UC Laboratory Fees Research Program (LFR-20-653926). We acknowledge support from the Physics Liquid Helium Laboratory Fund. The study at Tohoku University was supported by Grants-in-Aid for Early Career Scientists (Grant No. 20K14395), Scientific Research on Innovative Areas (Grants No. 19H05824), Scientific Research (A) (Grant No. 22H00101), Challenging Research (Exploratory) (Grant No. 19K21839), the Fund for the Promotion of Joint International Research (Fostering Joint International Research; Grant No. 19KK0069) from the Japan Society for the Promotion of Science, and the CORE Laboratory Research Program “Dynamic Alliance for Open Innovation Bridging Human, Environment and Materials” of the Network Joint Research Center for Materials and Device. The experiments at JRR-3 (proposal No. 22900) and the travel expenses for the neutron scattering experiment at ANSTO were partly supported by the General User Program for Neutron Scattering Experiments, Institute for Solid State Physics, University of Tokyo.

Appendix A: Synthesis method

The synthesis of the polycrystalline CeVGe₃ sample was prepared using the arc-melting method, followed by annealing the as-grown ingot sealed in a quartz tube at 850 °C for 15 days. Single crystals of CeVGe₃ were synthesized via the self-flux method. The starting materials [Ce pieces (Ames Lab), V pieces (etched with nitric acid), Ge lumps (6N)] were initially arc-melted to ensure a homogeneous mixture. The initial composition of elements is Ce : V : Ge = 4 : 1 : 19. To synthesize large single crystals that are suitable for NMR and neutron scattering study, we modify the temperature profile compared with the previous reports [15, 19]. The arc-melted mixture was placed in a 2 mL Canfield Crucible Set [44], and sealed in a fused silica ampoule in a partial pressure of argon. The sealed ampoule was placed in a furnace where it was held at 1200 °C for 10 hours, and slowly cooled to 860 °C over 210 hours. At 860 °C, the ampoule was removed from the furnace and quickly centrifuged to separate the single crystals from the molten flux. The largest single crystal we managed to grow is about 70 mg.

Appendix B: Hyperfine coupling

There are six nearest neighbor Ce ions to each V in CeVGe₃, and these are arranged in a hexagonal array such that three are above the V and three are below. The general form of the hyperfine coupling between a moment $\mathbf{m}(\mathbf{r})$ on the Ce located at \mathbf{r} and the nuclear spin \mathbf{I} on the V site is:

$$\mathcal{H}_{hf} = \gamma \hbar \mathbf{I} \cdot \sum_{i=1}^6 \mathbb{B}_i \cdot \mathbf{m}(\mathbf{r}_i) \quad (\text{B1})$$

where the hyperfine coupling matrices are:

$$\mathbb{B}_i = \begin{pmatrix} B_{i,aa} & B_{i,ab} & B_{i,ac} \\ B_{i,ab} & B_{i,bb} & B_{i,bc} \\ B_{i,ac} & B_{i,bc} & B_{i,cc} \end{pmatrix} \quad (\text{B2})$$

for each of the six nearest neighbors. These are related to one another by various symmetries. For example, $\{\mathbb{B}_1, \mathbb{B}_3, \mathbb{B}_5\}$ and $\{\mathbb{B}_2, \mathbb{B}_4, \mathbb{B}_6\}$ rotate into one another by $\frac{2\pi}{3}$ rotations about z , and that the second set is related to the first by both a $\frac{\pi}{3}$ rotation around z and a mirror reflection across the ab plane. As a result, there are only 6 independent quantities $B_{\alpha\beta}$.

We can compute the Knight shift tensor by assuming that $\langle \mathbf{m} \rangle = \chi \mathbf{H}_0$ is uniform. This leads a diagonal tensor with elements $K_{aa} = K_{bb} = 6B_{\perp}\chi_{aa}$ and $K_{cc} = 3B_{\parallel}\chi_{cc}$, where $B_{\perp} = (B_{aa} + B_{bb})/2$, and $B_{\parallel} = B_{cc}$. We can measure these quantities experimentally by comparing $K_{\alpha\alpha}$ and $\chi_{\alpha\alpha}$ to determine the components B_{\perp} and B_{\parallel} as discussed in the text.

Below T_N in the helical phase the ordered moments are given by: $\mathbf{m}(\mathbf{r}) = m_0 \{ \cos(2\pi k_z z/c), \sin(2\pi k_z z/c), 0 \}$, the internal hyperfine field lies in the ab plane and is given by $H_{hf} = H_{hf}^0 \{ \cos(2\pi k_z z'/c), \sin(2\pi k_z z'/c), 0 \}$, where $H_{hf}^0 = 6B_{\perp}m_0 |\cos(2\pi k_z z_0/c/2)|$ and $z' = z - c/2$.

Appendix C: Neutron scattering

Neutron powder diffraction experiments were carried out using the high-resolution powder diffractometer Echidna installed at the OPAL reactor, Australian Nuclear Science and Technology Organisation (ANSTO) with a neutron wavelength of 2.4395 Å selected by the Ge 331 reflection. The mass of the CeVGe₃ powder sample used in the neutron powder diffraction experiment was approximately 4.42 g. For the single crystal neutron diffraction experiments, the GPTAS (4G) triple-axis thermal neutron spectrometer without the analyzer (double-axis mode) installed at JRR-3, Tokai, Japan was used with the incident neutron energy of 14.7 meV and vertically focusing PG 002 monochromator. An additional PG filter was inserted after monochromator to suppress the higher harmonic neutron contribution. The CeVGe₃ single crystal with dimensions of $3 \times 2 \times 1$ mm³ and a mass of approximately 30 mg was aligned with two

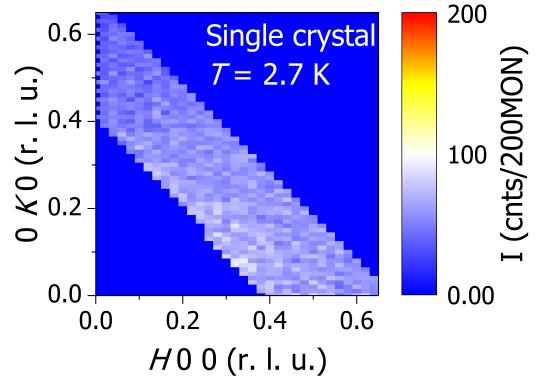


FIG. 11. Two-dimensional mesh scan at 2.7 K, revealing the absence of any satellite magnetic reflections in the $HK0$ plane.

scattering planes, $HK0$ and HHL , and then sealed in a standard aluminum sample can with ⁴He exchange gas. A Gifford-McMahon (GM) cooler, which was a ⁴He closed cycle refrigerator, was utilized to cool down the sample to a base temperature of 2.7 K. 1D reciprocal-space scans along the $(0, 0, L)$ and $(1, 1, L)$ directions were conducted to collect the integrated intensity to obtain the squared structure factor. The Lorentz factor was numerically corrected in the analysis.

TABLE I. The refined crystallographic data, numbers of nuclear reflections, and reliable factors of CeVGe₃ at 12 K. The isotropic displacement B_{iso} parameter for three atoms is fixed to 0.1 to reduce the number fitting parameters. The profile $R_p = \sum_i |y_{obs} - y_{calc}| / \sum_i y_{obs}$, and the weighted profile $R_{wp} = [\sum_i w_i |y_{obs} - y_{calc}|^2 / \sum_i w_i y_{obs}^2]^{1/2}$; The expected $R_{exp} = [(N - P + C) / \sum w_i y_{obs}^2]^{1/2}$.

CeVGe₃
 Hexagonal $P6_3/mmc$, (No. 194), $T = 12$ K (Echidna)
 $a = 6.1988(1)$ Å, $b = 6.1988(1)$ Å, $c = 5.6470(1)$ Å
 $\alpha = 90^\circ$, $\beta = 90^\circ$, $\gamma = 120^\circ$
 Number of fitting parameters 21
 Number of nuclear reflections 30

Atom	Site	x	y	z	B_{iso} (Å ²)
Ce	2d	1/3	2/3	3/4	0.1
V	2a	0	0	0	0.1
Ge	6h	0.1954 (2)	0.3908 (3)	1/4	0.1

$$R_p = 12.9\%, R_{wp} = 16.6\%, R_{exp} = 2.22\%, \chi^2 = 55.8$$

TABLE II. The allowed irreducible representations for the Ce 2d sites within the $P6_3/mmc$ space group, considering the magnetic modulation vector $\vec{k} = (0, 0, 0.49)$. The notation for the moment direction is given as (m_a, m_b, m_c) , where m_c is parallel to the sixfold axis and m_a and m_b are along the a and b axes, respectively, forming an angle of 120 degrees. Here $a = \cos(\pi \cdot 0.49)$ and $b = \sin(\pi \cdot 0.49)$

Allowed IRs	(1/3, 2/3, 3/4)	(2/3, 1/3, 1/4)
IR2:BV1	(0, 0, 1)	(0, 0, $a + bi$)
IR3:BV1	$(1 - (1/\sqrt{3})i, -(2/\sqrt{3})i, 0)$	$(-a - (1/\sqrt{3})b - (b - (1/\sqrt{3})a)i, -(2/\sqrt{3})b + (2/\sqrt{3})ai, 0)$
IR3:BV2	$(-(2/\sqrt{3})i, 1 - (1/\sqrt{3})i, 0)$	$(-(2/\sqrt{3})b + (2/\sqrt{3})ai, -a - (1/\sqrt{3})b - (b - (1/\sqrt{3})a)i, 0)$
IR5:BV1	(0, 0, 1)	(0, 0, $-a - bi$)
IR6:BV1	$(1 - (1/\sqrt{3})i, -(2/\sqrt{3})i, 0)$	$(a + (1/\sqrt{3})b + (b - (1/\sqrt{3})a)i, (2/\sqrt{3})b - (2/\sqrt{3})ai, 0)$
IR6:BV2	$(-(2/\sqrt{3})i, 1 - (1/\sqrt{3})i, 0)$	$((2/\sqrt{3})b - (2/\sqrt{3})ai, a + (1/\sqrt{3})b + (b - (1/\sqrt{3})a)i, 0)$

TABLE III. The fixed parameters of CeVGe₃ are used to estimate the magnetic moment size at 3.0 K.

CeVGe₃
 Hexagonal $P6_3/mmc$, (No. 194), $T = 3$ K (Echidna)
 $a = 6.19865(1)$ Å, $b = 6.19865(1)$ Å, $c = 5.6468(1)$ Å
 $\alpha = 90^\circ$, $\beta = 90^\circ$, $\gamma = 120^\circ$

Atom	Site	x	y	z	B_{iso} (Å ²)
Ce	2d	1/3	2/3	3/4	0.1

Number of refined parameters: 1
 Number of magnetic reflections: 15

Atom	Site	$ M $
Ce	2d	$0.38(3)\mu_B$

[1] H. v. Löhneysen, A. Rosch, M. Vojta, and P. Wölfle, Fermi-liquid instabilities at magnetic quantum phase transitions, *Rev. Mod. Phys.* **79**, 1015 (2007).

[2] G. R. Stewart, Non-Fermi-liquid behavior in *d*- and *f*-electron metals, *Rev. Mod. Phys.* **73**, 797 (2001).

[3] S. Paschen and Q. Si, Quantum phases driven by strong correlations, *Nature Review Physics* **3**, 9 (2020).

[4] S. Doniach, The Kondo lattice and weak antiferromagnetism, *Physica* **91B**, 231 (1977).

[5] P. Coleman, C. Pepin, Q. M. Si, and R. Ramazashvili, How do Fermi liquids get heavy and die?, *J. Phys.: Condens. Matter* **13**, R723 (2001).

[6] P. Gegenwart, Q. Si, and F. Steglich, Quantum criticality in heavy-fermion metals, *Nat. Phys.* **4**, 186 (2008).

[7] T. Park, F. Ronning, H. Q. Yuan, M. B. Salamon, R. Movshovich, J. L. Sarrao, and J. D. Thompson, Hidden magnetism and quantum criticality in the heavy fermion superconductor CeRhIn₅, *Nature* **440**, 65 (2006).

[8] J. Thompson, M. Nicklas, V. Sidorov, E. Bauer, R. Movshovich, N. Curro, and J. Sarrao, Interplay of magnetism, structure and superconductivity in heavy-fermion systems CeMIn₅ and PuMgGa₅, *J. Alloys Compd.* **408**, 16 (2006).

[9] V. A. Sidorov, M. Nicklas, P. G. Pagliuso, J. L. Sarrao, Y. Bang, A. V. Balatsky, and J. D. Thompson, Superconductivity and quantum criticality in CeCoIn₅, *Phys. Rev. Lett.* **89**, 157004 (2002).

[10] E. Schuberth, M. Tippmann, L. Steinke, S. Lausberg, A. Steppke, M. Brando, C. Krellner, C. Geibel, R. Yu, Q. Si, and F. Steglich, Emergence of superconductivity in the canonical heavy-electron metal YbRh₂Si₂, *Science* **351**, 485 (2016).

[11] L. Prochaska, X. Li, D. C. MacFarland, A. M. Andrews, M. Bonta, E. F. Bianco, S. Yazdi, W. Schrenk, H. Detz, A. Limbeck, Q. Si, E. Ringe, G. Strasser, J. Kono, and S. Paschen, Singular charge fluctuations at a magnetic quantum critical point, *Science* **367**, 285 (2020).

[12] F. Steglich, J. Aarts, C. D. Bredl, W. Lieke, D. Meschede, W. Franz, and H. Schäfer, Superconductivity in the presence of strong Pauli paramagnetism: CeCu₂Si₂, *Phys. Rev. Lett.* **43**, 1892 (1979).

[13] M. B. Maple, J. W. Chen, Y. Dalichaouch, T. Kohara, C. Rossel, M. S. Torikachvili, M. W. McElfresh, and J. D. Thompson, Partially gapped fermi surface in the heavy-electron superconductor URu₂Si₂, *Phys. Rev. Lett.* **56**, 185 (1986).

[14] H. Bie and A. Mar, Structure and magnetic properties of hexagonal perovskite-type rare-earth vanadium germanides REVGe₃ (RE = La–Nd), *J. Mater. Chem.* **19**, 6225 (2009).

[15] M. Inamdar, A. Thamizhavel, and S. K. Dhar, Anisotropic magnetic behavior of single crystalline CeTiGe₃ and CeVGe₃, *J. Phys.: Condens. Matter* **26**, 326003 (2014).

[16] S. Nakatsuji, S. Yeo, L. Balicas, Z. Fisk, P. Schlottmann, P. G. Pagliuso, N. O. Moreno, J. L. Sarrao, and J. D. Thompson, Intersite coupling effects in a Kondo lattice, *Phys. Rev. Lett.* **89**, 106402 (2002).

[17] A. K. Mitchell and L. Fritz, Kondo effect in three-dimensional Dirac and Weyl systems, *Phys. Rev. B* **92**, 121109 (2015).

[18] A. D. Christianson, E. D. Bauer, J. M. Lawrence, P. S. Riseborough, N. O. Moreno, P. G. Pagliuso, J. L. Sarrao, J. D. Thompson, E. A. Goremychkin, F. R. Trouw, M. P. Hehlen, and R. J. McQueeney, Crystalline electric field effects in CeMIn₅ (*m* = Co, Ir, and Rh): Superconductivity and the influence of Kondo spin fluctuations, *Phys. Rev. B* **70**, 134505 (2004).

[19] H. Jin, W. Cai, J. Coles, J. R. Badger, P. Klavins, S. Deepmyad, and V. Taufour, Suppression of ferromagnetism governed by a critical lattice parameter in CeTiGe₃ with hydrostatic pressure or V substitution, *Phys. Rev. B* **106**, 075131 (2022).

[20] W. Kittler, Ph.D. thesis, Karlsruhe Institute of Technology (2014).

[21] M. Majumder, W. Kittler, V. Fritsch, H. v. Löhneysen, H. Yasuoka, and M. Baenitz, Competing magnetic correlations across the ferromagnetic quantum critical point in the Kondo system CeTi_{1-x}V_xGe₃: ⁵¹V NMR as a local probe, *Phys. Rev. B* **100**, 134432 (2019).

[22] N. Curro, B. Young, J. Schmalian, and D. Pines, Scaling in the emergent behavior of heavy-electron materials, *Phys. Rev. B* **70**, 235117 (2004).

[23] K. R. Shirer, A. C. Shockley, A. P. Dioguardi, J. Crocker, C. H. Lin, N. apRoberts Warren, D. M. Nisson, P. Klavins, J. C. Cooley, Y.-f. Yang, and N. J. Curro, Long range order and two-fluid behavior in heavy electron materials, *Proc. Natl. Acad. Sci.* **109**, E3067 (2012).

[24] M. Jiang, N. J. Curro, and R. T. Scalettar, Universal Knight shift anomaly in the periodic Anderson model, *Phys. Rev. B* **90**, 241109 (2014).

[25] P. Menegasso, J. C. Souza, I. Vinograd, Z. Wang, S. P. Edwards, P. G. Pagliuso, N. J. Curro, and R. R. Urbano, Hyperfine couplings as a probe of orbital anisotropy in heavy-fermion materials, *Phys. Rev. B* **104**, 035154 (2021).

[26] T. Willers, F. Strigari, Z. Hu, V. Sessi, N. B. Brookes, E. D. Bauer, J. L. Sarrao, J. D. Thompson, A. Tanaka, S. Wirth, L. H. Tjeng, and A. Severing, Correlation between ground state and orbital anisotropy in heavy fermion materials, *Proc. Natl. Acad. Sci.* **112**, 2384 (2015).

[27] N. Curro, P. Hammel, P. Pagliuso, J. Sarrao, J. Thompson, and Z. Fisk, Evidence for spiral magnetic order in the heavy fermion material CeRhIn₅, *Phys. Rev. B* **62**, R6100 (2000).

[28] Y.-f. Yang and D. Pines, Emergent states in heavy-electron materials, *Proc. Natl. Acad. Sci.* **109**, E3060 (2012).

[29] Y.-F. Yang and D. Pines, Universal behavior in heavy-electron materials, *Phys. Rev. Lett.* **100**, 096404 (2008).

[30] N. apRoberts Warren, A. P. Dioguardi, A. C. Shockley, C. H. Lin, J. Crocker, P. Klavins, and N. J. Curro, Commensurate antiferromagnetism in CePt₂In₇, a nearly two-dimensional heavy fermion system, *Phys. Rev. B* **81**, 180403 (2010).

[31] T. Moriya, The effect of electron-electron interaction on the nuclear spin relaxation in metals, *J. Phys. Soc. Jpn.* **18**, 516 (1963).

[32] T. Moriya and K. Ueda, Nuclear magnetic relaxation in weakly ferro- and antiferromagnetic metals, *Solid State*

Commun. **15**, 169 (1974).

[33] T. Mito, S. Kawasaki, G.-q. Zheng, Y. Kawasaki, K. Ishida, Y. Kitaoka, D. Aoki, Y. Haga, and Y. Onuki, Pressure-induced anomalous magnetism and unconventional superconductivity in CeRhIn₅: ¹¹⁵In-NQR study under pressure, *Phys. Rev. B* **63**, 220507 (2001).

[34] Y. Kawasaki, S. Kawasaki, M. Yashima, T. Mito, G. qing Zheng, Y. Kitaoka, H. Shishido, R. Settai, Y. Haga, and Y. Onuki, Anisotropic spin fluctuations in heavy-fermion superconductor cecoin₅: In-NQR and Co-NMR studies, *J. Phys. Soc. Jpn.* **72**, 2308 (2003).

[35] G.-q. Zheng, K. Tanabe, T. Mito, S. Kawasaki, Y. Kitaoka, D. Aoki, Y. Haga, and Y. Onuki, Unique spin dynamics and unconventional superconductivity in the layered heavy fermion compound CeIrIn₅: NQR evidence, *Phys. Rev. Lett.* **86**, 4664 (2001).

[36] I. Vinograd, K. R. Shirer, P. Massat, Z. Wang, T. Kissikov, D. Garcia, M. D. Bachmann, M. Horvatić, I. R. Fisher, and N. J. Curro, Second order Zeeman interaction and ferroquadrupolar order in TmVO₄, *npj Quantum Materials* **7**, 68 (2022).

[37] T. Nagamiya, K. Nagata, and Y. Kitano, Magnetization Process of a Screw Spin System, *Prog. Theor. Phys.* **27**, 1253 (1962).

[38] W. Bao, P. G. Pagliuso, J. L. Sarrao, J. D. Thompson, Z. Fisk, J. W. Lynn, and R. W. Erwin, Incommensurate magnetic structure of CeRhIn₅, *Phys. Rev. B* **62**, R14621 (2000).

[39] S. Raymond, E. Ressouche, G. Knebel, D. Aoki, and J. Flouquet, Magnetic structure of CeRhIn₅ under magnetic field, *J. Phys.: Condens. Matter* **19**, 242204 (2007).

[40] S. Mishra, A. Demuer, D. Aoki, and I. Sheikin, Specific heat of CeRhIn₅ in high magnetic fields: Magnetic phase diagram revisited, *Phys. Rev. B* **103**, 045110 (2021).

[41] P. Das, S.-Z. Lin, N. J. Ghimire, K. Huang, F. Ronning, E. D. Bauer, J. D. Thompson, C. D. Batista, G. Ehlers, and M. Janoschek, Magnitude of the magnetic exchange interaction in the heavy-fermion antiferromagnet CeRhIn₅, *Phys. Rev. Lett.* **113**, 246403 (2014).

[42] T. Willers, Z. Hu, N. Hollmann, P. O. Körner, J. Gegner, T. Burnus, H. Fujiwara, A. Tanaka, D. Schmitz, H. H. Hsieh, H.-J. Lin, C. T. Chen, E. D. Bauer, J. L. Sarrao, E. Goremychkin, M. Koza, L. H. Tjeng, and A. Severing, Crystal-field and Kondo-scale investigations of CeMIn₅ (*m* = Co, Ir, and Rh): A combined x-ray absorption and inelastic neutron scattering study, *Phys. Rev. B* **81**, 195114 (2010).

[43] J. Shim, K. Haule, and G. Kotliar, Modeling the localized to itinerant electronic transition in the heavy fermion system CeIrIn₅, *Science* **318**, 1615 (2007).

[44] P. C. Canfield and Z. Fisk, Growth of single crystals from metallic fluxes, *Philos. Mag. B* **65**, 1117 (1992).