

Type of the Paper (Article, Review, Communication, etc.)

Macroscopic biaxial order in multilayer films of bent-core liquid crystals deposited by combined Langmuir-Blodgett/Langmuir-Schaefer technique

Francesco Vita ^{1,*}, Fabrizio Corrado Adamo ¹, Mario Campana ², Federica Ciuchi ³, Maria Penelope De Santo ³, Daniel Hermida-Merino ⁴, XXXXXX ¹, Michela Pisani ¹, Diego Pontoni ⁵, Eric Scharrer ⁶ and Oriano Francescangeli ^{2,*}

- ¹ SIMAU Department, Polytechnic University of Marche, Via Brecce Bianche, 60131 Ancona, Italy; f.c.adamo@staff.univpm.it (F.C.A.); m.pisani@univpm.it (M.P.)
- ² ISIS Neutron and Muon Source, Rutherford Appleton Laboratory, Harwell, UK; mario.campana@stfc.ac.uk
- ³ CNR-Nanotec c/o Physics Department, University of Calabria, Ponte Bucci, Cubo 31C, 87036 Arcavacata di Rende, Italy; federica.ciuchi@cnr.it (F.C.); maria.desanto@fis.unical.it (M.P.D.S.)
- ⁴ CINBIO, Departamento de Fisica Aplicada, Universidade de Vigo, Campus Lagoas-Marcosende, Vigo 36310, Spain; xxxxxxx
- ⁵ Partnership for Soft Condensed Matter, European Synchrotron Radiation Facility, 38043 Grenoble, France; diego.pontoni@esrf.fr
- ⁶ Department of Chemistry, University of Puget Sound, Tacoma, WA 98416, USA; escharrer@pugetsound.edu (E.S.)
- * Correspondence: f.vita@univpm.it (F.V.); o.francescangeli@univpm.it (O.F.)

Abstract: Bent-core liquid crystals, a class of mesogenic compounds with non-linear molecular structure, are well-known for their unconventional mesophases, characterized by complex molecular (and supramolecular) ordering and often featuring biaxial and polar properties. In the nematic phase their unique behavior is manifested in the formation of nano-sized biaxial clusters of layered molecules (cybotactic groups). While this prompted their consideration in the quest for nematic biaxiality, experimental evidence indicates that cybotactic order is only short-ranged and that the nematic phase is macroscopically uniaxial. By combining atomic force microscopy, neutron reflectivity and wide-angle grazing-incidence X-ray scattering, here we demonstrate that multilayer films of a bent-core nematic, deposited on silicon by a combined Langmuir-Blodgett and Langmuir-Schaefer approach, exhibit macroscopic in-plane ordering, with the long molecular axis tilted with respect to the sample surface and the short molecular axis (*i.e.*, the apex bisector) aligned along the film compression direction. We thus propose the use of Langmuir films as an effective way to study and control the complex anchoring properties of bent-core liquid crystals.

Keywords: liquid crystals; bent-core mesogens; Langmuir films; grazing-incidence wide-angle X-ray scattering; neutron reflectivity

Citation: To be added by editorial staff during production.

Academic Editor: Firstname Last-name

Received: date

Revised: date

Accepted: date

Published: date



Copyright: © 2023 by the authors. Submitted for possible open access publication under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).

1. Introduction

Among the several different mesophases formed by liquid crystalline materials, the nematic (N) phase of calamitic (*i.e.* rod-like) liquid crystals (LCs) is by far the most well-known, in particular as it provides the basis for the widespread LC display technology. Its fundamental feature is the spontaneous alignment of the molecules' long axes along a common average direction, denoted by the molecular director **n**. As a consequence, all the physical properties of a N material are strongly anisotropic, with a characteristic uniaxial symmetry.

For the N phase to be of any practical utility, it is necessary to control the orientation of the $\mathbf{n}$ director over macroscopic distances. In typical LC devices, this task is accomplished by imposing anisotropic surface anchoring conditions at the confining boundaries, which force $\mathbf{n}$ to align along a predetermined preferential direction; once the ground state orientation of $\mathbf{n}$ has been established, it can then be switched through the torque exerted by an external electric field.

However, theoretical considerations do not forbid the possibility of a biaxial N phase, where the average orientation of the long molecular axis along $\mathbf{n}$ is accompanied by the preferential alignment of a molecular transverse axis along a secondary director $\mathbf{m}$ orthogonal to $\mathbf{n}$ [1,2]. Still, the biaxial N phase has remained elusive, with no undisputable evidence reported until now for low molecular weight calamitic LCs [3,4]. Over the last two decades, bent-core mesogens (BCMs), a class of compounds featuring a kinked aromatic core between by two terminal aliphatic tails, have emerged as promising candidates for nematic biaxiality [5,6]. In fact, although the occurrence of spontaneous macroscopic biaxiality in nematic BCMs has been questioned, strong experimental evidence suggests the presence of local biaxial (and possibly polar) order within nanosized clusters of stratified molecules (known as cybotactic groups) which permeate the N phase. While the clusters' transverse axes are randomly oriented in the unperturbed N phase, resulting in an overall uniaxial mesophase, proper external stimuli can align the clusters, extending biaxial (and possibly polar) order over a macroscopic length scale [7-11].

A critical issue for the experimental study of BCMs, as well as for their use in electro-optical devices, is the ability to finely control the orientation of the N director by means of proper anchoring conditions. Unfortunately, surface treatments known to be effective for aligning conventional nematics often provide unexpected results when used with BCMs [12-14]. Notably, this ambiguity in the alignment of BCMs has resulted in conflicting interpretations of several experiments, *e.g.*, with observations of the uniaxial-biaxial N phase transition being subsequently interpreted in terms of anchoring transitions in a uniaxial N phase [15-17]. As a matter of fact, the experimental demonstration of N biaxiality in any LC system would be extremely eased by the ability to align both $\mathbf{n}$ and $\mathbf{m}$ directors by means of biaxial anchoring conditions.

An unconventional strategy to tackle the BCM alignment problem is the deposition of BCM Langmuir films: mesogens spread over water form a thin layer at the water-air interface, with molecular packing controlled by the pressure exerted on the film by a movable barrier; once the desired molecular arrangement has been obtained, the film can be transferred onto a solid substrate. This technique represents a valuable tool to determine the surface alignment of BCMs and to study their anchoring properties. The resulting films are of interest by themselves, *e.g.* in the case of ferroelectric liquid crystals, or they can be used as aligning substrates for bulk liquid crystals [18-33].

Recently, we have used this approach to deposit thin films of a BCM known as OC4-2MePh(mono2MeODBP) [33]. It belongs to a much-studied family of laterally methylated BCMs featuring an oxadiazole bisphenol core and short butoxy terminal chains (Figure 1a-b) [34-38]. The N phase of these mesogens exhibits a few peculiarities: the possibility to be supercooled to room temperature and strong evidence (from X-ray diffraction data) of locally biaxial molecular ordering [35,38]. The formation of stable Langmuir films in these BCMs is remarkable as their chemical structure, with two hydrophobic tails and a more hydrophilic core, is significantly different from that of typical amphiphilic molecules. In fact, the complex BCM interaction with the water sub-phase in Langmuir films is responsible for the unusual bilayer structure of deposited films revealed by X-ray reflectivity (XRR) measurements: an upper layer of upright molecules and a bottom layer of flat molecules, so as to minimize the terminal tails' interaction with the water and, after deposition, with the substrate (hydrophilic silicon oxide) (Figure 1c) [33].

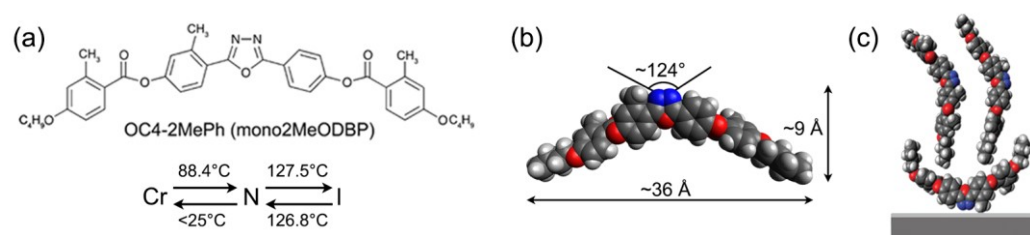


Figure 1. (a) Chemical structure of mesogen OC4-2MePh(mono2MeODBP) with the relative phase transition temperatures on heating and cooling: crystalline phase (Cr) – nematic phase (N) – isotropic phase (I). (b) Optimized molecular geometry. (c) Structure of a Langmuir film deposited on a silicon substrate (with a thin silicon oxide layer at the interface), according to [33].

While XRR can elucidate the film structure in the direction orthogonal to the substrate, it is blind to in-plane order. The latter can be conveniently investigated by means of grazing-incidence wide-angle X-ray scattering (GIWAXS). Unfortunately, because of their chemical structure (lacking heavy atoms) and short-range positional order, liquid crystals exhibit weak and diffuse diffraction features. As a result, films obtained with a single deposition were too thin to generate a detectable diffraction signal. To address this problem, we describe here the preparation of multilayer samples via repeated Langmuir-Blodgett (LB)/Langmuir-Schaefer (LS) deposition. GIWAXS measurements performed on these samples reveal a tilted, smectic-C like, molecular stratification and a macroscopic in-plane ordering: the films are thus biaxial. The structure of deposited films is compared with that of Langmuir films over water, investigated by means of neutron reflectivity (NR). The results provide further insight into the BCM assembly at the air-water interface, showing that molecular ordering is substantially preserved during the deposition process.

2. Materials and Methods

2.1. Mesogen synthesis

The synthesis of OC4-2MePh(mono2MeODBP) has been described elsewhere [34]. Its chemical structure, typical dimensions in the fully extended configuration, and mesophase diagram are shown in Figure 1a,b.

2.2. Sample preparation

Langmuir films of OC4-2MePh(mono2MeODBP) over water were prepared in a NIMA Langmuir trough equipped with control barriers (NIMA Technology Ltd., Coventry, England). A 0.1 mg/mL solution of OC4-2MePh(mono2MeODBP) in chloroform was spread over pure water (resistivity of 18.2 MΩ/cm); the latter was obtained from an ELGA PURELAB Flex water purification system (ELGA LabWater, Wycombe, UK). After evaporation of the solvent, the film was compressed by closing the control barriers at a constant rate of 70 cm²/min from an initial area per molecule of $A \approx 130 \text{ Å}^2$. Compression isotherms (surface pressure Π vs. area per molecule APM) were measured using a Wilhelmy plate pressure sensor.

Multilayer samples were obtained by repeated film depositions on silicon substrates ((111)-cut *p*-doped), previously treated with piranha solution. Using (111)-cut silicon prevented the appearance of Bragg reflections in the q -range of interest for GIWAXS experiments. The deposition pressure was set at $\Pi = 30 \text{ mN/m}$, corresponding to an area per molecule of $APM \approx 32 \text{ Å}^2$. The deposition of the first layer was performed with the LB technique, *i.e.* by extraction of a vertical substrate immersed in the water before formation of the Langmuir film (Figure 2a). Subsequently, 28 additional layers (for a total of 29 layers) were deposited using the LS configuration (Figure 2b): in this case, the substrate, kept parallel to the water surface, was gently lowered until getting in contact with the Lang-

muir film, which was hence transferred onto the silicon. In the LS depositions the substrate orientation was chosen in such a way that the barrier compression direction was parallel to the substrate extraction direction of the first LB deposition. We denote this direction by the in-plane vector $\mathbf{c}$. Finally, excess water was left to evaporate.

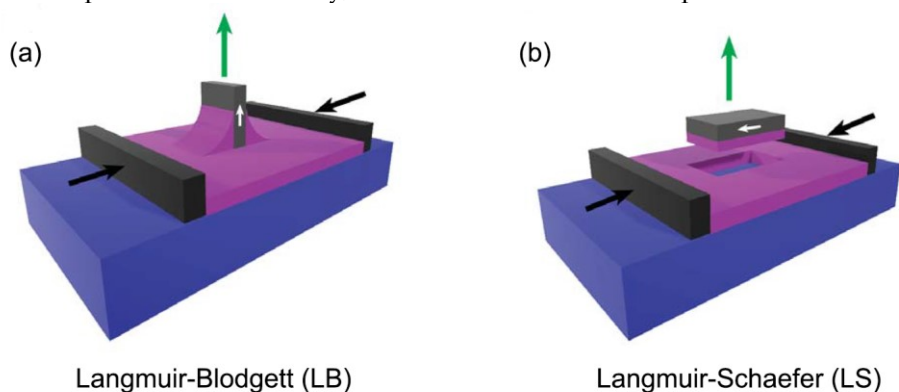


Figure 2. Schematic drawing of the deposition set-up, with the Langmuir film (purple) being transferred from the water (blue) onto the silicon substrate (gray): (a) LB technique used to transfer the first layer; (b) LS technique used to deposit the subsequent 28 layers. The orientation of the substrate during the LB and LS deposition phases is indicated by the in-plane vector $\mathbf{c}$ (white arrow).

2.3. Atomic force microscopy measurements

Samples obtained by a single LB deposition on silicon were investigated by atomic force microscopy (AFM) using a Multimode 8 AFM microscope equipped with a Nanoscope V controller (Bruker, Santa Barbara, USA). Data were acquired in tapping mode using silicon cantilevers (model TAP150, Bruker, Santa Barbara, USA).

2.4. Neutron reflectivity measurements

NR measurements on Langmuir films were performed at the Surf beamline of ISIS Neutron and Muon Source (Rutherford Appleton Laboratory, United Kingdom) [39] using a polychromatic neutron beam with wavelength λ between 0.5 and 7 Å. Measurements were performed at three different angles ($\theta = 0.35, 0.65$ and 1.5°) to cover a suitable q range:

$$q = \frac{2\pi \sin \theta}{\lambda}.$$

Measurements were performed in 2 different contrasts (sub-phases) to ensure maximum sensitivity to the layer adsorbed at the interface. While the use of null-reflecting water (NRW) is particularly sensitive to adsorbed amount at the interface, the use of D₂O enables the resolution of the interfacial structure.

Langmuir films of OC4-2MePh(mono2MeODBP) were prepared using a NIMA trough with an area of 20×30 cm² (NIMA Technology Ltd., Coventry, England). A 0.1 mg/mL solution of OC4-2MePh(mono2MeODBP) in chloroform was spread on each sub-phase. Measurements were taken at a fixed surface pressure of 30 mN/m. The compression isotherms measured in this condition did not significantly differ from those measured during the previously described sample preparation experiments. In particular, the area per molecule calculated from the trough area at 30 mN/m was ~ 36 Å², very close to the value of ~ 32 Å² measured in deposition experiments.

The two contrasts were co-fitted using the in-house built software Rascal. A Bayesian analysis of the fit was then used to associate appropriate confidence interval to the optimum fitted values. The reflectivity profiles were co-fitted modelling the air-water interface as a finite stack of layers, each layer being characterised by a certain thickness t , an interlayer roughness σ and a scattering length density Nb_{layer} . The scattering length density of a layer is:

$$Nb_{\text{layer}} = \sum_i N_i b_i,$$

where N_i and b_i are the number density and the scattering length for the i -th species present in the layer, respectively. The latter can be calculated from composition for the BCM, D₂O and H₂O: $b_{BCM} = 169.07 \text{ fm molec}^{-1}$, $b_{D_2O} = 19.145 \text{ fm molec}^{-1}$ and $b_{H_2O} = -1.67 \text{ fm molec}^{-1}$ (note how mixing ~8% of D₂O and 92% of H₂O leads to NRW with $b_{NRW} = 0$). D₂O often presents some H₂O contamination and its Nb may be lower than the theoretical value of $6.35 \times 10^{-6} \text{ \AA}^{-2}$. The D₂O used in this study had an $Nb = 6.21 \times 10^{-6} \text{ \AA}^{-2}$, as calculated from the critical edge q_c observed ($q_c = \sqrt{16\pi\Delta Nb}$, where ΔNb is the difference in Nb between the two bulk phases, air and D₂O).

When using NRW, the reflectivity is solely originating from the interfacial monolayer. Under these conditions, the adsorbed amount per unit area Γ and the corresponding area per molecule APM can be calculated from the experimentally determined parameters Nb_{layer} and t :

$$\Gamma = \frac{Nb_{layer} t}{b_{BCM} N_A}$$

where N_A is Avogadro's number [40]. The APM is then calculated as:

$$APM = \frac{1}{N_A \Gamma}$$

The fitting of the experimental data, performed via scripting in Rascal, used as fitting parameters for each layer the thickness t , the APM and, where applicable, the percentage of hydration water. No roughness was required to fit the reflectivity data. We set the interlayer roughness at 0.5 Å in order to get smoother transitions in the Nb profiles, hence a better visualization of the plots.

2.5. Grazing-incidence wide-angle X-ray scattering measurements

The in-plane and out-of-plane order of multilayer films on silicon was investigated by GIWAXS. The measurements were carried out at the NCD-SWEET beamline of the ALBA synchrotron, Barcelona (Spain). The sample was mounted on a rotating stage allowing measurements under different azimuthal orientations (the φ angle between the beam incidence plane and the film compression direction $\mathbf{c}$, as shown in Figure 3). The beam energy was 8 keV (wavelength $\lambda = 1.55 \text{ \AA}$) and the beam size was $111 \times 12 \text{ }\mu\text{m}^2$ (width $\times$ height). The sample-to-detector distance was $D = 198.4 \text{ mm}$ and the fixed incident angle was set at $\alpha_{in} = 0.16 \text{ deg}$, leading to an irradiated area on the sample of $\sim 0.5 \text{ mm}^2$. All the patterns were recorded at room temperature, with an exposure time of 30 s, using a LX255-HS detector (Rayonix, Evanston, USA).

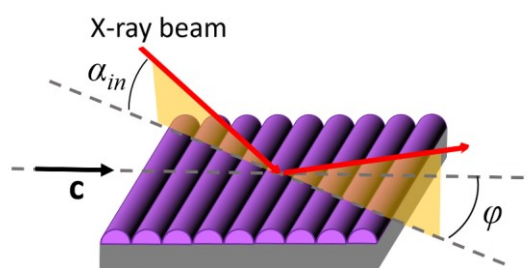


Figure 3. GIWAXS geometry. The drawing highlights the presence of film undulations (purple) along the $\mathbf{c}$ vector, as discussed in section 3.1 and 3.3.

3. Results and discussion

3.1. Preliminary Langmuir film characterization

A typical compression isotherm of OC4-2MePh(mono2MeODBP) over water is shown in Figure 4. The sudden pressure drop at the end of the compression curve indicates the collapse of the film occurring at $\Pi \approx 39$ mN/m. Below this threshold, the isotherm is characterized by a plateau at the pressure of ~ 10 mN/m, during which the area per molecule decreases from ~ 120 to ~ 60 Å² with only a minimal increase of the surface pressure, followed by a steep increase of the pressure. In our previous work, we interpreted the plateau as due to the coalescence and internal reorganization of the initially floating monolayer domains, with the final formation of a more stable, uniform and tightly packed double molecular layer in correspondence of the pressure increase [33]. Consequently, in that case we chose the end of the plateau, at a pressure of 12 mN/m, as set point for the film deposition. However, the resulting film morphology was still not very homogenous, with AFM images showing the formation of fibrous supramolecular structures locally aligned with each other but with no long range orientational order (Figure 5a).

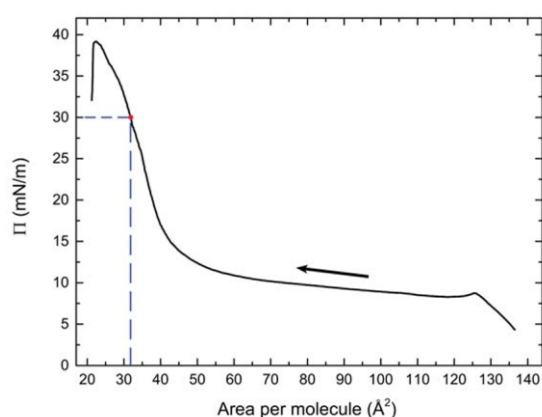


Figure 4. Compression isotherm of the BCM Langmuir film. The arrow indicates the compression direction; the dashed lines point out the deposition parameters.

Aiming at getting a more uniform coverage of the substrate and, above all, a more ordered packing of the molecules, for the present work we chose a higher deposition pressure of 30 mN/m, corresponding to an area per molecule of ~ 32 Å². To investigate the effect of the large deposition pressure on the film morphology, a single LB deposition on silicon was examined by AFM (Figure 5b–d). The difference with films deposited at $\Pi = 12$ mN/m is evident. The film is now much more uniform; the fibrous meandering structure present in low pressure samples is replaced here by dense sequence of parallel grooves, homogeneously aligned along the direction perpendicular to the dipping direction **c** (Figure 5b,c). These undulations have a width of ~ 100 nm and a depth of ~ 3 nm (Figure 5d), values quite similar to those observed in samples deposited at lower pressure. Clearly, the higher deposition pressure results in a more ordered mesoscale structure, characterized by an in-plane anisotropy extending uniformly over the sample surface.

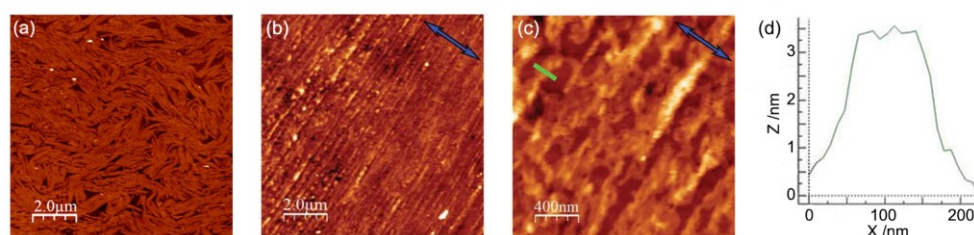


Figure 5. (a) AFM image of a single LB deposition on silicon at $\Pi = 12$ mN/m, from [33]. (b,c) AFM images of a single LB deposition on silicon at $\Pi = 30$ mN/m at different magnifications. The blue

arrows indicate the compression direction **c.** **(d)** Thickness profile measured along the green bar in **(c)**.

3.2. Neutron reflectivity measurements

To further investigate the effect the increased deposition pressure on the film morphology, NR measurements were performed on the BCM Langmuir film representing conditions prior to deposition, at a fixed pressure of 30 mN/m. Figure 6a shows the reflectivity curves measured on D₂O and NRW along with the best line fits; the corresponding *Nb* profiles are shown in Figure 6b together with a molecular model of the interfacial layer. The shaded areas correspond to the 65% confidence intervals. Attempts to fit the reflectivity profiles through a one-layer model proved unsuccessful. Satisfactory results were obtained with the addition of a second layer. The fit results indicate that the upper layer (Layer 1) contains only BCM molecules (no hydration); this is often observed within Langmuir monolayers where the hydrophobic part is expelled out of the aqueous phase and the Van der Waals interactions within the monolayer ensure tight packing. The lower layer (Layer 2) consists of BCM and water and represents a diffuse layer on the aqueous side of the interface. It must be stressed that modelling this diffuse layer on the air side of the interface (*i.e.*, as layer composed of air and BCM molecules) leads to an unsatisfactory fit of the data.

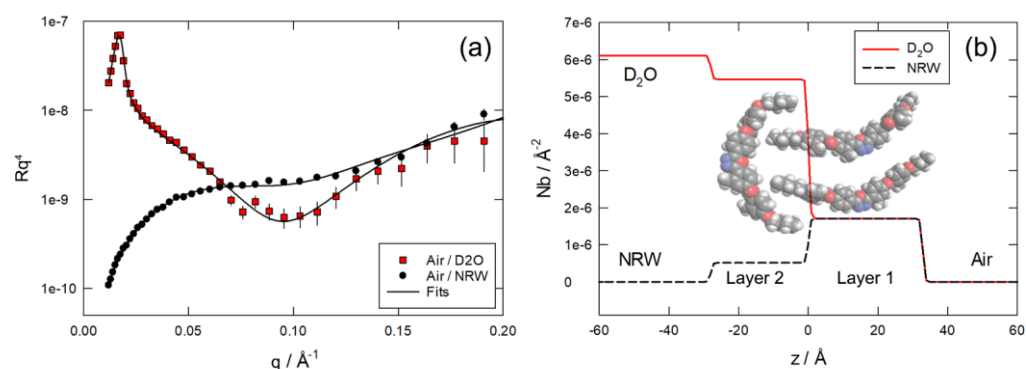


Figure 6. **(a)** Reflectivity profiles for the BCM layer at the air/water interface, plotted as Rq^4 vs q , with R indicating the reflectivity. Red squares represent the data for the air/D₂O interface; black circles correspond to the air/NRW interface. The solid lines represent the best fit to the data. **(b)** Scattering length density profiles for the BCM layer at the air/water interface with the proposed molecular model. Red and black solid lines correspond to D₂O and NRW runs, respectively. The zero of the z axis has been arbitrarily positioned at the interface between Layer 1 and Layer 2, which represents the boundary between air and water (Layer 1 is entirely out of the water phase, Layer 2 is immersed in the bulk).

The fitted parameters, together with the 65% confidence interval, are summarised in Table 1. The thickness of the upper layer (~ 27.8 Å) is significantly lower than the extended full length of the molecule (~ 36 Å). Thus, it is consistent with an emerged layer of tilted BCM molecules. In fact, the measured value is very close to the layer thickness provided by GIWAXS for deposited multilayer films (25.1 Å), where molecules assume a tilted configuration (as discussed in the next section). However, considering the fact that we have little sensitivity to the C₄H₉ terminal tails, particularly the one exposed to the air phase (the *Nb* of the tails alone would be very similar to that of air), and the possibility that the lower tails of the upper layer may be protruding into the bottom layer, we cannot completely rule out a configuration of Layer 1 with straight BCMs, which only get tilted after deposition.

The APM within this layer is ~ 30.5 Å², indicating that the BCM molecules are very well-ordered within the monolayer. This small APM value is evidently incompatible with

the molecules lying flat. Also in this case, the APM is very close to the value estimated by GIWAXS for deposited multilayers ($33.8 \text{ \AA}^2$), further supporting the conclusion that the tilted molecular arrangement observed in deposited films is already present in the Langmuir film prior to deposition.

Table 1. Results of fitting the NR curves: fitted parameters, best fit values, 65% confidence interval, and limits of variation. The background parameters indicate the level of uncoherent scattering from the sample.

Parameter	Fitted value	65% confidence interval	Limits (min-max)
Layer 1 thickness / $\text{\AA}$	27.8	23.1, 32.3	1-50
Layer 2 thickness / $\text{\AA}$	24.8	22.5, 31.1	1-50
Layer 1 APM / $\text{\AA}^2$	30.5	28.5, 37.1	1-50
Layer 2 APM / $\text{\AA}^2$	77.5	57.4, 110.0	1-150
Layer 2 hydration / %	77.0	53.4, 78.8	0-100
Background D ₂ O / $\times 10^{-6}$	1.65	0.89, 7.70	0.1-100
Background NRW / $\times 10^{-6}$	6.15	3.30, 7.24	0.1-100

The thickness of the bottom layer is slightly smaller, but it is highly hydrated (~77% water in the layer) and contains considerably less material (~28% of the overall interfacial BCM content). The latter percentage is similar to the results of previous XRR measurements on deposited films, which revealed a ratio of 1.92 : 1 between the number of molecules in the top and in the bottom layer [33]. The larger value of APM for Layer 2 ($77.5 \text{ \AA}^2$, quite close to the value of $69.1 \text{ \AA}^2$ obtained from XRR measurements in anhydrous conditions) would suggest an arrangement with the molecules lying flat with lifted terminal tails. However, the high level of hydration and the layer thickness, large for a layer of flat molecules, rather indicate a highly dispersed layer of relatively disordered molecules.

In evaluating the details of the film structure, one should also consider that our two-layer model necessarily provide a simplified picture, as it does not take into account the variation Nb across the BCM molecules (core vs. tails) and the possibility of a partial layer intermixing (e.g., by tail interdigitation) which would make the boundary between the two layers somewhat ill-defined. Actually, the total thickness of the interfacial film is $52.8 \text{ \AA}$, a value very close to that of $49 \text{ \AA}$ obtained by XRR for dry Langmuir films deposited on silicon at a pressure of 12 mN/m . Considering the different deposition pressure and the different content of water, the results of the two techniques are in substantial agreement in describing the system.

3.3. Grazing-incidence wide-angle X-ray scattering measurements

The multilayer films deposited on silicon with the combined LB/LS methodology described in section 2.2 were characterized by GIWAXS, with the geometry shown in Figure 3. Typical diffraction patterns measured for $\varphi = 0$ (incidence plane parallel to **c**) and $\varphi = \pi/2$ (incidence plane perpendicular to **c**) are shown in Figure 7a and 7b, respectively. The difference between the two diffraction patterns is a clear indication of the sample in-plane anisotropy, already evidenced by the AFM scans. However, while the anisotropy observed by AFM is relative to the mesoscale sample morphology, the GIWAXS data pertain to a much lower length scale, revealing the anisotropy of the molecular ordering.

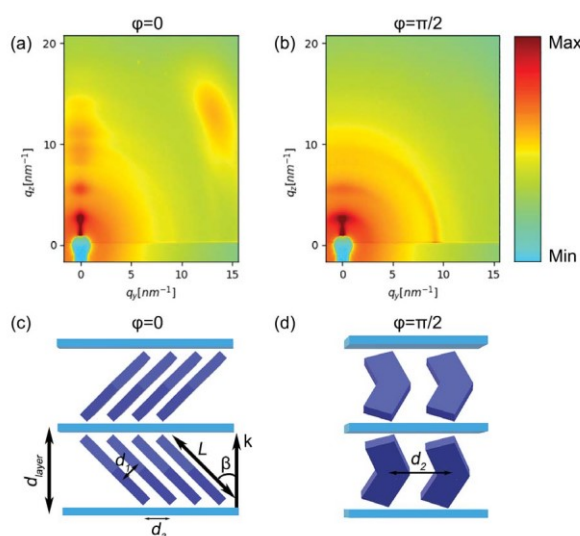


Figure 7. GIWAXS diffraction patterns for different azimuthal orientations of the sample: (a) incidence plane of the X-ray beam parallel to the film compression direction $\mathbf{c}$ ($\varphi = 0$); (b) incidence plane perpendicular to the film compression direction $\mathbf{c}$ ($\varphi = \pi/2$). Only the right half of the patterns is shown because of the pattern symmetry. The diffraction intensity is color-coded on a logarithmic scale. On the lower panel, scheme of the layered molecular arrangement for different azimuthal orientations: (c) $\varphi = 0$ and (d) $\varphi = \pi/2$.

Looking into the details of the GIWAXS patterns, it is possible to notice a sequence of reflections centered at $q_y = 0$. They consist of a fundamental reflection at $q_z = 2.5 \text{ nm}^{-1}$ and the corresponding higher orders. These reflections, present in both patterns, are clearly related to the multilayer nature of the sample and correspond to an interlayer distance $d_{\text{layer}} = 25.1 \text{ \AA}$. This value is significantly lower than the molecular length ($L = 36 \text{ \AA}$). Assuming no intercalation, it suggests a tilt of the molecules, with the molecular long axis forming an angle $\beta = \cos^{-1}(d_{\text{layer}}/L) = 46^\circ$ with the layer normal (Figure 7c).

Comparing this sequence of reflections in the two patterns, it can be noticed that they are much more intense and transversally narrow in the pattern taken at $\varphi = 0$ (Figure 7a). By contrast, a significant transverse broadening affects the reflections in the patterns taken at $\varphi = \pi/2$ (Figure 7b), which also smears out the diffraction intensity. This effect is attributed to the presence of grooves similar to those evidenced by AFM scans for single LB depositions (Figure 5b–d), *i.e.*, to undulations of the layers propagating along the Langmuir film compression direction $\mathbf{c}$ as shown in Figure 3.

Figure 7a also shows a broad oblique reflection in the wide-angle region, approximately centered at ($q_y \approx 13.3 \text{ nm}^{-1}$, $q_z \approx 12.7 \text{ nm}^{-1}$). The same feature is absent in the pattern taken at $\varphi = \pi/2$. The $\mathbf{q}$ vector of this reflection forms an angle of $\sim 46^\circ$ with the layer normal; this value exactly matches the angle β estimated above and corresponds to an intermolecular distance $d_1 \approx 3.4 \text{ \AA}$, the typical value of the intermolecular distance between stacked aromatic groups. Based on these observations, we attribute the wide-angle reflection to the transverse (face-to-face) positional correlation between close-packed mesogens, tilted with respect to the layer normal, as schematically shown in Figure 7c. As typical in fluid liquid crystal systems, this transverse correlation is very short-ranged, as indicated by the breadth of the corresponding reflection. Finally, the disappearance of this oblique reflection for $\varphi = \pi/2$ indicates that the molecules tilt in the plane orthogonal to the compression direction $\mathbf{c}$. Although the diffraction patterns at $\varphi = 0$ (Figure 7a) only shows one wide-angle reflection (because of the detector being off-center), a rotation of the sample by π results in the same diffraction pattern. This symmetry implies an equivalent number of molecules tilted to the right and to the left of the $\mathbf{c}$ direction. This could be due, for

example, to the presence of domains with opposite tilt as well as to layers with alternate tilt directions, as shown in the model of Figure 7c.

For $\varphi = \pi/2$, the wide-angle diffraction feature is substituted by an in-plane peak centered at ($q_y = 9.1 \text{ nm}^{-1}$, $q_z = 0 \text{ nm}^{-1}$). It corresponds to a d -spacing $d_2 = 6.9 \text{ \AA}$, which can be interpreted as the transverse intermolecular distance measured in the plane of the mesogen cores (Figure 7d). While the transverse broadening of this reflection may be once again attributed to the film undulations, this diffraction feature is rather narrow in the radial direction (along q_y). This indicates a relatively long-ranged positional order in the plane of the film, along the compression direction. The layer area associated to each molecule can be calculated as the product of d_2 and $d_3 = \frac{d_1}{\cos \beta} = 4.9 \text{ \AA}$ (see Figure 7c,d), obtaining a value of $33.8 \text{ \AA}^2$ in excellent agreement with the APM value estimated by NR measurement on the water subphase.

5. Conclusions

The NR measurements performed on Langmuir films substantially confirm the complex nature of BCM assemblies over water, with the mesogens organizing in a double molecular layer, most likely to decrease the interaction with water of the hydrophobic terminal chains. The top layer is tightly packed and lies entirely above the water surface, whereas the bottom layer is more diffuse and totally submerged. Transferring the Langmuir film on a solid substrate via LB deposition preserves this double layer structure (with the bottom layer assuming a more ordered configuration upon water evaporation), as formerly demonstrated [33]. Here, we showed that subsequent depositions via LS methodology results in biaxial film, made of a stack of titled molecules with in-plane anisotropy. The layer thickness and the APM measured in the deposited films are very close to the corresponding values in the top layer of the Langmuir films, indicating that the tilted molecular ordering is already present at the water-air interface and is preserved in the deposition process. Apparently, after the first LB deposition, the more diffuse bottom layer of the Langmuir film does not take part into the subsequent LS depositions and does not affect the final film structure.

A remarkable feature of the deposited films is their in-plane anisotropy: considering the large investigate area in the GIWAXS geometry, it extends homogeneously over macroscopic distances. This peculiar arrangement is clearly related to the anisotropy of the sample production method, with the compression direction breaking the in-plane symmetry of the Langmuir film. It is interesting to observe that the in-plane anisotropy (and hence the film biaxiality) manifests itself at several levels: on the mesoscale, in the formation of grooves uniformly aligned along the c direction; on the molecular length scale, in the tilt of the long molecular axis in the plane orthogonal to c and in the coherent alignment of the molecular transverse axes (proper biaxiality). The last effect is not entirely new for OC4-2MePh(mono2MeODBP), as X-ray diffraction measurements evidenced a strong tendency to local biaxial packing in the N phase of this mesogen [35–38]. However, in the bulk such ordering averages out over macroscopic distances resulting in a uniaxial N phase, as proved by a thorough optical investigation [17]. The described deposition technique represents, hence, an effective strategy to enhance the BCM natural tendency to biaxial ordering, forcing the mesogens to adopt a uniform organization over a large area.

Although the phase diagram of OC4-2MePh(mono2MeODBP) does not show any smectic mesophase, the “artificial” structure of our films resembles that of the well-known SmCP (or B₂) phase of BCMs, a tilted smectic phase featuring polar (ferroelectric or anti-ferroelectric) properties [22,23,41]. While we did not perform any electro-optical characterization of our films, this aspect certainly deserves further investigation. Another interesting question to be elucidated is whether the mesoscale undulations observed in our films could be caused by a frustration mechanism similar to that originating saddle splay layer distortion in the so called helical nanofilament (HNF) phases of BCMs [41–43].

Author Contributions: Conceptualization, F.V. and O.F.; methodology, F.V., F.C.A., M.C., M.P.; formal analysis, F.C.A., M.C.; investigation, F.V., F.C.A., M.C., F.C., M.P.D.S., D. H.-M., M.P.; resources, F.C., M.P.D.S., D.P., E.S.; data curation, F.V., F.C.A., M.C.; writing—original draft preparation, F.V., F.C.A., M.C.; writing—review and editing, F.V., M.P., O.F.; visualization, F.V., F.C.A., M.C.; supervision, F.V., O.F.; project administration, F.V.; funding acquisition, F.V., E.S., O.F. All authors have read and agreed to the published version of the manuscript.

Funding: This research received no external funding.

Data Availability Statement: We encourage all authors of articles published in MDPI journals to share their research data. In this section, please provide details regarding where data supporting reported results can be found, including links to publicly archived datasets analyzed or generated during the study. Where no new data were created, or where data is unavailable due to privacy or ethical restrictions, a statement is still required. Suggested Data Availability Statements are available in section “MDPI Research Data Policies” at <https://www.mdpi.com/ethics>.

Acknowledgments: We acknowledge ALBA Synchrotron (Spain) for the provision of beamtime and Eduardo Solano of the NCD-SWEET beamline for technical assistance in the measurements. We acknowledge Nicola Scaramuzza (Università della Calabria, Italy) and the staff of the Partnership for Soft Condensed Matter (PSCM) at the European Synchrotron Radiation Facility (ESRF) for their support.

Conflicts of Interest: The authors declare no conflict of interest.

References

- Freiser, M.J. Ordered states of a nematic liquid. *Phys. Rev. Lett.* **1970**, *24*, 1041–1043. <https://doi.org/10.1103/PhysRevLett.24.1041>
- Biaxial nematic liquid crystals: theory, simulation, and experiment*; Luckhurst, G.R., Sluckin, T.J., Eds.; John Wiley & Sons, Ltd: Chichester, United Kingdom, 2015.
- Luckhurst, G.R. Biaxial liquid crystals, fact or fiction? *Thin Solid Films* **2001**, *393*, 40–52. [https://doi.org/10.1016/S0040-6090\(01\)01091-4](https://doi.org/10.1016/S0040-6090(01)01091-4)
- Tschierske, C.; Photinos, D.J. Biaxial nematic phases. *J. Mater. Chem.* **2010**, *20*, 4263–4294. <https://doi.org/10.1039/B924810B>
- Jákli, A. Liquid crystals of the twenty-first century—nematic phase of bent-core molecules. *Liq. Cryst. Rev.* **2013**, *1*, 65–82. <https://doi.org/10.1080/21680396.2013.803701>
- Vita, F. Search for nematic biaxiality in bent-core mesogens: An X-ray diffraction perspective. *Liq. Cryst.* **2016**, *43*, 2254–2276. <https://doi.org/10.1080/02678292.2016.1204634>
- Vanakaras, A.G.; Photinos, D.J. Thermotropic biaxial nematic liquid crystals: spontaneous or field stabilized?. *J. Chem. Phys.* **2008**, *128*, 154512. <https://doi.org/10.1063/1.2897993>
- Samulski, E.T. Meta-cybotaxis and nematic biaxiality. *Liq. Cryst.* **2010**, *37*, 669–678. <https://doi.org/10.1080/02678292.2010.488938>
- Francescangeli, O.; Stanic, V.; Torgova, S.I.; Strigazzi, A.; Scaramuzza, N.; Ferrero, C.; Dolbnya, I.; Weiss, T.; Berardi, R.; Muccioli, L.; Orlandi, S.; Zannoni, C. Ferroelectric response and induced biaxiality in the nematic phase of bent-core mesogens. *Adv. Funct. Mater.* **2009**, *19*, 2592–2600. <https://doi.org/10.1002/adfm.200801865>
- Francescangeli, O.; Vita, F.; Ferrero, C.; Dingemans, T.; Samulski, E.T. Cybotaxis dominates the nematic phase of bent-core mesogens: a small-angle diffuse X-ray diffraction study. *Soft Matter* **2011**, *7*, 895–901. <https://doi.org/10.1039/C0SM00745E>
- Francescangeli, O.; Vita, F.; Samulski, E.T. The cybotactic nematic phase of bent-core mesogens: state of the art and future developments. *Soft Matter* **2014**, *10*, 7685–7691. <https://doi.org/10.1039/C4SM01256A>
- Elamain, O.; Hegde, G.; Komitov, L. Alignment and alignment transition of bent core nematics. *Appl. Phys. Lett.* **2013**, *103*, 023301. <https://doi.org/10.1063/1.4813443>
- Yoon, H.G.; Kang, S.W.; Lehmann, M.; Park, J.O.; Srinivasaraode, M.; Kumar, S. Homogeneous and homeotropic alignment of bent-core uniaxial and biaxial nematic liquid crystals. *Soft Matter* **2011**, *7*, 8770–8775. <https://doi.org/10.1039/C1SM05653K>
- Kumar, T.A.; Le, K.V.; Kim, J.K.; Takezoe, H.; Dhara, S. Alignment of unconventional nematic liquid crystals. *Liq. Cryst.* **2011**, *38*, 917–924. <https://doi.org/10.1080/02678292.2011.585522>
- Senyuk, B.; Wonderly, H.; Mathews, M.; Li, Q.; Shiyanovskii, S.V.; Lavrentovich, O.D. Surface alignment, anchoring transitions, optical properties, and topological defects in the nematic phase of thermotropic bent-core liquid crystal A131. *Phys. Rev. E* **2010**, *82*, 041711. <https://doi.org/10.1103/PhysRevE.82.041711>
- Kim, Y.; Cukrov, G.; Xiang, J.; Shin, S.; Lavrentovich, O.D. Domain walls and anchoring transitions mimicking nematic biaxiality in the oxadiazole bent-core liquid crystal C7. *Soft Matter* **2015**, *11*, 3963–3970. <https://doi.org/10.1039/C5SM00580A>
- Kim, Y.K.; Cukrov, G.; Vita, F.; Scharrer, E.; Samulski, E.T.; Francescangeli, O.; Lavrentovich, O.D. Search for microscopic and macroscopic biaxiality in the cybotactic nematic phase of new oxadiazole bent-core mesogens. *Phys. Rev. E* **2016**, *93*, 062701. <https://doi.org/10.1103/PhysRevE.93.062701>
- Kinoshita, Y.; Park, B.; Takezoe, H.; Niori, T.; Watanabe, J. Visualization of the molecular shape and the orientational distribution in the Langmuir-Blodgett film of a bent-shaped achiral molecule as studied by surface second-harmonic generation. *Langmuir* **1998**, *14*, 6256–6260. <https://doi.org/10.1021/la980542i>
- Zou, L.; Wang, J.; Beleva, V.J.; Kooijman, E.E.; Primak, S.V.; Risse, J.; Weissflog, W.; Jákli, A.; Mann, E.K. Langmuir monolayers of bent-core molecules. *Langmuir* **2004**, *20*, 2772–2780. <https://doi.org/10.1021/la0361924>
- Wang, J.; Zou, L.; Weissflog, W.; Jákli, A.; Mann, E.K. Anisotropy in Langmuir layers of a bent-core liquid crystal. *Langmuir* **2006**, *22*, 3198–3206. <https://doi.org/10.1021/la0531805>
- Wang, J.; Qiu, L.; Jákli, A.; Weissflog, W.; Mann, E.K. Inverse Langmuir–Schaefer films of bent-core molecules. *Liq. Cryst.* **2010**, *37*, 1229–1236. <https://doi.org/10.1080/02678292.2010.494739>
- Blinov, L.M.; Palto, S.P.; Lazarev, V.V.; Geivandov, A.R.; Yudin, S.G. Antiferroelectric and ferroelectric switching of a liquid crystal in Langmuir–Blodgett films under strong confinement conditions. *Crystallogr. Rep.* **2006**, *51*, 843–849. <https://doi.org/10.1134/S1063774506050154>
- Geivandov, A.R.; Alto, S.P.; Yudin, S.G.; Blinov, L.M.; Pelzl, G.; Weissflog, W. Ferro- and antiferroelectric properties of Langmuir–Blodgett films composed of mesogenic bent-core molecules. *Ferroelectrics* **2006**, *344*, 3–10. <https://doi.org/10.1080/00150190600966748>
- García-Vázquez, P.; Morales-Saavedra, O.G.; Pelzl, P.; Guadalupe Bañuelos, J.; Carreón-Castro, M.P. Incorporation in Langmuir and Langmuir–Blodgett films of symmetric fluorine substituted bent-core liquid crystals: Morphological and optical properties. *Thin Solid Films* **2009**, *517*, 1770–1777. <https://doi.org/10.1016/j.tsf.2008.10.017>
- Giner, I.; Gascón, I.; Vergara, J.; López, M.C.; Ros, M.B.; Royo, F.M. Molecular arrangement in Langmuir and Langmuir–Blodgett films of a mesogenic bent-core carboxylic acid. *Langmuir* **2009**, *25*, 12332–12339. <https://doi.org/10.1021/la901614p>
- Smith, T.J.; Iglesias, W.; Stefanovic, S.R.; Mann, E.K.; Tschierske, C.; Jákli, A.; Lacks, D.J. Effects of tether length on the behavior of amphiphilic bent-core molecules at water surfaces. *J. Phys. Chem. B* **2011**, *115*, 12809–12815. <https://doi.org/10.1021/jp207918y>
- Iglesias, W.; Smith, T.J.; Basnet, P.B.; Stefanovic, S.R.; Tschierske, C.; Lacks, D.J.; Jákli, A.; Mann, E.K. Alignment by Langmuir/Schaefer monolayers of bent-core liquid crystals. *Soft Matter* **2011**, *7*, 9043–9050. <https://doi.org/10.1039/C1SM05546A>

28. Kaur, R.; Bhullar, G.K.; Rao, N.V.S.; Raina, K.K. Effect of pH on the control of molecular orientation in monolayer of bent-core liquid crystal materials by Langmuir–Blodgett method. *Liq. Cryst.* **2015**, *42*, 8–17. <https://doi.org/10.1080/02678292.2014.956352>
29. Smith, T.J.; Iglesias, W.; Mann, E.K.; Jáklí, A.; Lacks, D.J. Alignment of nematic liquid crystals by a bent-core substrate. *Liq. Cryst.* **2013**, *40*, 159–164. <https://doi.org/10.1080/02678292.2012.735705>
30. Choudhary, K.; Gupta, R.K.; Pratibha, R.; Sadashiva, B.K.; Manjuladevi, V. Alignment of liquid crystals using Langmuir Blodgett films of unsymmetrical bentcore liquid crystals. *Liq. Cryst.* **2019**, *46*, 1494–1504. <https://doi.org/10.1080/02678292.2019.1574035>
31. Baidya, A.; Das, B.; Majumder, S.; Saha, S.K.; Nath, R.K.; Paul, M.K. The aggregation of 1,3,4-thiadiazole based Hockey stick shaped Mesogen in Langmuir–Blodgett thin film in comparison to that of 1,3,4-oxadiazole. *J. Surf. Sci. Technol.* **2021**, *37*, 43–66. <https://doi.org/10.18311/jsst/2021/28356>
32. Baidya, A.; Das, B.; Majumder, S.; Saha, S.K.; Nath, R.K.; Paul, M.K. The unique asymmetric nano-cluster formation by the uneven hockey-stick-shaped mesogen based on 1,3,4-oxadiazole in Langmuir–Blodgett thin film. *J. Dispersion Sci. Technol.* **2022**, *43*, 1208–1218. <https://doi.org/10.1080/01932691.2020.1848584>
33. Adamo, F.C.; Ciuchi, F.; De Santo, M.P.; Astolfi, P.; Warner, I.; Scharrer, E.; Pisani, M.; Vita, F.; Francescangeli, O. Nanoscale structure of Langmuir–Blodgett film of bent-core molecules. *Nanomaterials* **2022**, *12*, 2285. <https://doi.org/10.3390/nano12132285>
34. Speetjens, F.; Lindborg, J.; Tauscher, T.; LaFemina, N.; Nguyen, J.; Samulski, E.T.; Vita, F.; Francescangeli, O.; Scharrer, E. Low nematic onset temperatures and room temperature cybotactic behavior in 1,3,4-oxadiazole-based bent-core mesogens possessing lateral methyl groups. *J. Mater. Chem.* **2012**, *22*, 22558–22564. <https://doi.org/10.1039/C2JM33705C>
35. Vita, F.; Tauscher, T.; Speetjens, F.; Samulski, E.T.; Scharrer, E.; Francescangeli, O. Evidence of biaxial order in the cybotactic nematic phase of bent-core mesogens. *Chem Mat.* **2014**, *26*, 4671–4674. <https://doi.org/10.1021/cm5019822>
36. Vita, F.; Tauscher, T.; Speetjens, F.; Ferrero, C.; Samulski, E.T.; Scharrer, E.; Francescangeli, O. Insights into biaxial ordering of bent-core nematics: X-ray diffraction evidence. *Mol. Cryst. Liq. Cryst.* **2015**, *611*, 171–179. <https://doi.org/10.1080/15421406.2015.1030232>
37. Nguyen, J.; Wonderly, W.; Tauscher, T.; Harkins, R.; Vita, F.; Portale, G.; Francescangeli, O.; Samulski, E.T.; Scharrer, E. The effects of lateral halogen substituents on the low-temperature cybotactic nematic phase in oxadiazole based bent-core liquid crystals. *Liq. Cryst.* **2015**, *42*, 1754–1764. <https://doi.org/10.1080/02678292.2015.1085599>
38. Harkins, R.; Tauscher, T.; Nguyen, J.; Lewis, S.; Adamo, F.C.; Pisani, M.; Hermida-Merino, D.; Samulski, E.T.; Vita, F.; Francescangeli, O.; Scharrer, E. Biaxial ordering in the supercooled nematic phase of bent-core mesogens: Effects of molecular symmetry and outer wing lateral groups. *Liq. Cryst.* **2020**, *47*, 1986–1998. <https://doi.org/10.1080/02678292.2019.1633431>
39. Penfold, J.; Richardson, R.M.; Zarbakhsh, A.; Webster, J.R.P.; Bucknall, D.G.; Rennie, A.R.; Jones, R.A.L.; Cosgrove, T.; Thomas, R.K.; Higgins, J.S.; Fletcher, P.D.I.; Dickinson, E.; Roser, S.J.; McLure, I.A.; Hillman, A.R.; Richards, R.W.; Staples, E.J.; Burgess, A.N.; Simister, E.A.; White, J.W. Recent advances in the study of chemical surfaces and interfaces by specular neutron reflection. *J. Chem. Soc., Faraday Trans.* **1997**, *93*, 3899–3917. <https://doi.org/10.1039/A702836I>
40. Zarbakhsh, A.; Campana, M.; Webster, J.R.P.; Wojciechowski, K. Stabilization of alkylated azacrown ether by fatty acid at the air-water interface. *Langmuir* **2010**, *26*, 18194–18198. <https://doi.org/10.1021/la103620b>
41. Eremin, A.; Jáklí, A. Polar bent-shape liquid crystals—From molecular bend to layer splay and chirality. *Soft Matter* **2013**, *9*, 615–637. <https://doi.org/10.1039/c2sm26780b>
42. Callahan, R.A.; Coffey, D.C.; Chen, D.; Clark, N.A.; Rumbles, G.; Walba, D.M. Charge generation measured for fullerene–helical nanofilament liquid crystal heterojunctions. *ACS Appl. Mater. Interfaces* **2014**, *6*, 4823–4830. <https://doi.org/10.1021/am405759d>
43. Hough, L.E.; Jung, H.T.; Krüerke, D.; Heberling, M.S.; Nakata, M.; Jones, C.D.; Chen, D.; Link, D.R.; Zasadzinski, J.; Heppke, G.; Rabe, J.P.; Stocker, W.; Körblova, E.; Walba, D.M.; Glaser, M.A.; Clark, N.A. Helical nanofilament phases. *Science* **2009**, *325*, 456–460. <https://doi.org/10.1126/science.1170027>

Disclaimer/Publisher’s Note: The statements, opinions and data contained in all publications are solely those of the individual author(s) and contributor(s) and not of MDPI and/or the editor(s). MDPI and/or the editor(s) disclaim responsibility for any injury to people or property resulting from any ideas, methods, instructions or products referred to in the content.