

ARTICLE

Elucidating Performance Degradation Mechanisms in Non-Fullerene Acceptor Solar Cells

Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

Vinod K. Sangwan,^{a,*,#} Zachary Martin,^{a,#} Guoping Li,^b Fei Qin,^b Shreyash Hadke,^a Robert M. Pankow,^b Woo Cheol Jeon,^b Ding Zheng,^b Yongjoon Cho,^b Ryan M. Young,^{b,*} Kevin L. Kohlstedt,^{b,*} Michael R. Wasielewski,^{b,*} George C. Schatz,^{b,*} Antonio Facchetti,^{b,c,*} Mark C. Hersam,^{a,b,d,*} and Tobin J. Marks^{b,*}

Organic solar cells (OSCs) using non-fullerene acceptors (NFAs) afford exceptional photovoltaic performance metrics, however, their stability remains a significant challenge. Existing OSC stability studies focus on understanding degradation rate-performance relationships, improving interfacial layers, and suppressing degradative chemical reaction pathways. Nevertheless, there is a knowledge gap concerning how such degradation affects crystal structure, electronic states, and recombination dynamics that ultimately impact NFA performance. Here we seek a quantitative relationship between OSC metrics and blend morphology, trap density of states, charge carrier mobility, and recombination processes during the UV-light-induced degradation of **PBDB-TF:Y6** inverted solar cells as the PCE (power conversion efficiency) falls from 17.3 to 5.0%. Temperature-dependent electrical and impedance measurements reveal deep traps at 0.48 eV below the conduction band that are unaffected by **Y6** degradation, and shallow traps at 0.15 eV below the conduction band that undergo a three-fold density of states increase at the PCE degradation onset. Computational analysis correlates vinyl oxidation with a new trap state at 0.25 eV below the conduction band, likely involving charge transfer from the UV-absorbing ZnO electron transport layer. *In-situ* integrated photocurrent analysis and transient absorption spectroscopy reveal that these traps lower electron mobility and increase recombination rates during degradation. Grazing-incidence wide-angle x-ray scattering and computational analysis reveal that the degraded **Y6** crystallite morphology is largely preserved but that <1% of degraded **Y6** molecules cause OSC PCE performance degradation by ≈50%. Together the detailed electrical, impedance, morphological, ultrafast spectroscopic, matrix-assisted laser desorption/ionization time-of-flight (MALDI-ToF) spectroscopy, and computational data reveal that the trap state energies and densities accompanying **Y6** vinyl oxidation are primarily responsible for the PCE degradation in these operating NFA-OSCs.

^a Department of Materials Science and Engineering, Northwestern University, Evanston, Illinois 60208 (USA)

^b Department of Chemistry, Northwestern University, Evanston, Illinois 60208 (USA)

^c School of Materials Science and Engineering, Georgia Institute of Technology, Atlanta, Georgia 30332 (USA)

^d Department of Electrical and Computer Engineering, Northwestern University, Evanston, Illinois 60208 (USA)

^e # Equal contributions

* Corresponding Authors.

Emails: vinod.sangwan@northwestern.edu, ryan.young@northwestern.edu, kkohlstedt@northwestern.edu, m-wasielewski@northwestern.edu, g-schatz@northwestern.edu, a-facchetti@northwestern.edu, t-marks@northwestern.edu, m-hersam@northwestern.edu

Electronic Supplementary Information (ESI) available: [details of any supplementary information available should be included here]. See DOI: 10.1039/x0xx00000x

INTRODUCTION

Organic solar cells (OSCs) based on bulk heterojunctions (BHJs) continue to evolve as a next-generation photovoltaic technology due to unprecedented power conversion efficiencies (PCEs), low-cost fabrication, mechanical flexibility, and earth-abundant, non-toxic elemental composition.^{1–9} Among different molecular and polymeric systems, non-fullerene acceptors (NFAs) have emerged as one of the most promising electron acceptors that can be paired with electron donor polymers to achieve OSCs with PCEs in excess of 19%.^{10–19} NFAs such as **ITIC**, **IT-4F**, **Y5**, and **Y6** not only possess favorable frontier energy levels that align well with donor polymers such as **PBDB-TF** (Fig. 1) and charge transport layers for efficient charge extraction but they also possess band gaps that can harvest infrared photons to generate additional charge carriers.^{3, 4, 20–27} Furthermore, NFA molecules offer tunability of frontier orbital energies from modular design with a diverse range of end groups, strong π - π interactions, excellent mixing properties in the BHJ blend, and very low internal reorganization energies upon photon capture.^{24, 27–31} This combination of properties has led to rapid progress in optimizing the device performance metrics by tailoring blend chemistry and morphology on demand.

Nevertheless, the practical deployment of OSCs requires improved stability to reach cost-effectiveness versus incumbent technologies.^{3, 5, 32–34} Thus far, NFA-based OSCs have shown limited PCE stability under continuous operation. Existing literature on stability either correlates performance metrics deterioration with various NFA chemical reaction pathways involving the final byproducts or reports empirical degradation rates of OSCs by varying constituent blends, interfacial layers, and device architecture.^{34–48} Thus, there is a knowledge gap in understanding the microscopic mechanism of how OSC degradation affects crystal structure, electronic structure, charge transport, and recombination dynamics in BHJ blends —properties that influence macroscopic performance metrics. Here, we study unencapsulated OSCs with an inverted geometry of ITO/ZnO/**PBDB-TF:Y6**/MoO₃/Ag (Fig. 1) as a model system that are degraded by exposure to simulated solar irradiation, where UV exposure is expected to reduce PCE monotonically with increasing exposure duration.³⁶ Here we systematically analyze the evolution of the trap density of states, charge carrier mobility, and recombination dynamics by *in-situ* measurements under operating conditions with controlled degradation. Concomitantly, we describe the measured trends in terms of trap energy and recombination dynamics by proposing a putative degradation pathway and calculating the density of states for the degraded NFA.

It will be seen that degradation leads to three main results that we have modeled using quantum mechanical computational analysis. (i) Variable temperature current-voltage (IVT) characteristics reveal that forward bias charge transport is dominated by a series resistance originating from deep-lying trap states located at 0.48 eV below the lowest unoccupied **Y6** molecular orbital (LUMO). Surprisingly, these trap states are not connected with the PCE degradation. (ii) Thermal admittance spectroscopy (TAS) of pristine **PBDB-TF:Y6** cells identifies a trap energy level at 0.15 eV that moves deeper into the bandgap (0.21 eV) with at least

a three-fold increase in the density of states upon initial PCE degradation from PCE = 17.3 to 11.1%. (iii) Integrated photocurrent device analysis (IPDA) reveals that electron mobility at the maximum power point falls roughly six-fold when PCE degrades by two-fold. As expected, increasing the number of trap states increases monomolecular recombination, whereas the bimolecular/geminate recombination coefficient under operating conditions decreases with degradation. (iv) Transient absorption spectroscopy of pure **Y6** and the BHJ **PBDB-TF:Y6** blend show increased kinetic rates of fast (ps) and slow (ns) processes upon degradation which is consistent with reduced mobility and increased geminate recombination. Thus, the trap energy levels from TAS correlate with the **Y6** degradation such that a relatively low density of degraded molecules (<1%) can introduce recombination and charge trapping sites with major losses in the cell performance — PCE loss by more than 50%. These results are consistent with the role of the electron transport layer ZnO in generating radicals under UV exposure^{36, 37} that can degrade **Y6** with only minuscule changes in the blend morphology,^{36, 37} as revealed here by grazing incidence wide-angle x-ray scattering (GIWAXS).

To complement the experimental input, parallel computational analysis provides a deeper understanding of the NFA degradation process, including the crystal structural changes and a molecular understanding of the trap states that are formed during degradation. In our model, we consider three likely degraded **Y6** structures: (a) vinyl oxidation between the core and end group, (b) acceptor end group scission, and (c) dicyanomethylene scission on the end group (See computational methods for structural details). These candidate structures represent three likely degradation pathways induced by UV-generated free radicals that can occur even some distance from the ETL interface. Of the three proposed degradation pathways, it will be seen that the vinyl oxidation pathway is the most likely degradation product based on the calculated density of states reproducing the measured trap energetics. Using the crystal structure of **Y6**, we generate a relaxed crystal of degraded **Y6** molecules and determine the frontier orbital energies of degraded **Y6** molecules. Based on the degraded crystal structure and density of states, we characterize the vinyl oxidized crystal structure and describe the evolution of a LUMO trap state 0.25 eV into the bandgap. Therefore, while the chemical degradation pathways further corroborate existing molecular degradation hypotheses,^{35, 36, 39, 49} this study provides new insight into the evolution of NFA electronics under PCE degrading irradiation.

From the combined experimental and theoretical work reported here, the shallow **Y6** trap states are identified and shown to become deeper even with minute amounts of degraded NFAs by well-structured *in-situ* measurements. Moreover, the electronic structure analysis of the NFA crystal structures matrix-assisted laser desorption/ionization time-of-flight (MALDI-ToF) spectroscopy clarifies that these trap states arise from vinyl oxidation, among the three aforementioned plausible reaction pathways that can be initiated by free radicals under UV exposure. These findings should provide insight into the design of future more stable NFA molecules and suggest replacing ZnO with other electron transport layers,

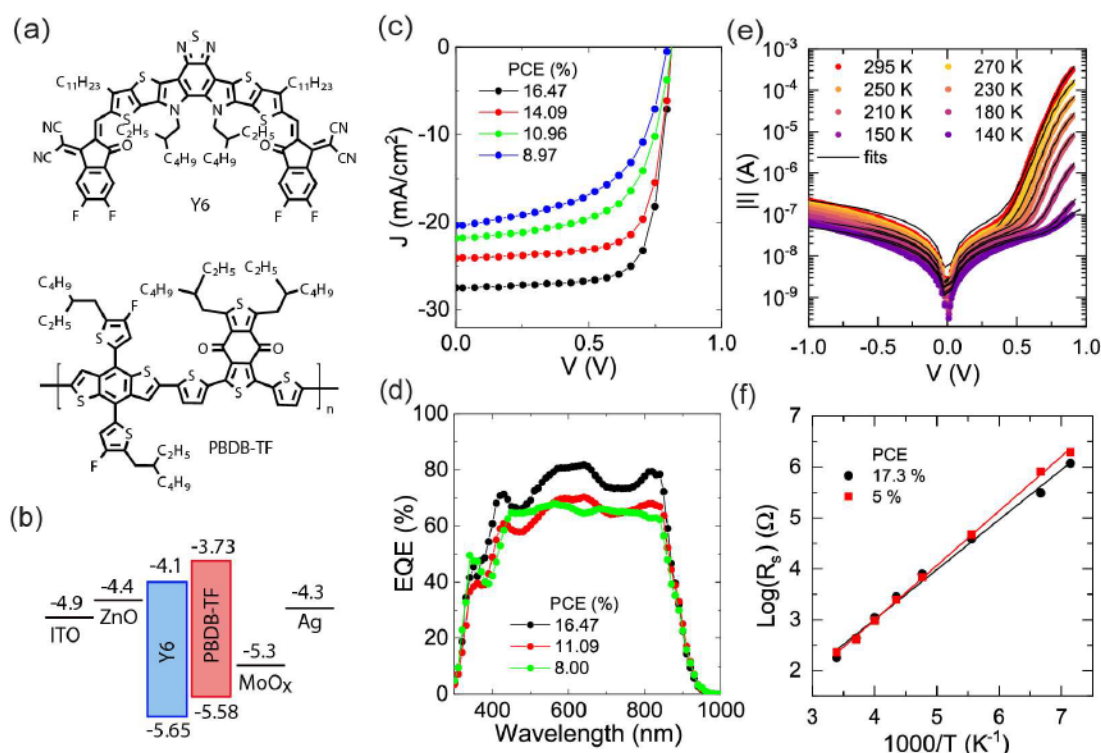


Figure 1. (a) Chemical structures of Y6 (top) and PBDB-TF (bottom) molecules. (b) Energy level alignment of the various layers in PBDB-TF:Y6 solar cells. (c) Current-density-voltage (J - V) characteristics of the solar cell at different PCE values during degradation. (d) External quantum efficiency (EQE) plot of the cell at different PCE values during degradation. (e) Dark J - V characteristics of a solar cell at varying temperatures from 140 – 295 K. Solid lines show fits to the Schottky diode equation. (f) Plot of $\text{Log}(R_s)$ versus $1/T$ to extract E_s for pristine and degraded cells.

passivating the ZnO, and/or designing NFA molecules with functionalized end groups to suppress vinyl linkage oxidation.

RESULTS AND DISCUSSION

Due to the variety of photophysical and structural characterizations described in this section, we have organized the main results into six subsections. The organization of this section is as follows: First discussed (Section A) are procedures for creating and monitoring PBDB-TF:Y6 degradation by variable temperature current-density-voltage measurements over a broad voltage range. The data are fit to a Shockley diode and a thermal activation model to extract key parameters including the location of deep traps in the energy band structure. Next, Section B focuses on quantifying the number, energy, and attempt frequency of shallow trap states in the pristine blend and then tracking their evolution with degradation by frequency- and temperature-dependent capacitance (CFT), and optical absorption spectroscopic measurements. Section C employs *in-situ* integrated photocurrent device analysis (IPDA) to study the evolution of mobility and recombination coefficient as OSCs are degraded systematically. In Section D, we then use transient absorption spectroscopy to probe the effects of OSC degradation on the excited-state dynamics, to assess the origins of the degraded OSC spectral signatures, hole transfer rates, and recombination kinetics.

Section E employs grazing-incidence wide-angle x-ray scattering (GIWAXS) to assess the structural integrity of the OSC bulk-heterojunction blend during the degradation process. Section F uses electronic structure computation and the experimental photophysical, diffraction, and MALDI-ToF data to understand the energies/chemistry of the trap states and how the Y6 molecule degrades. Here, we propose a putative degradation pathway by using computational modeling of the NFA band structure before and after degradation through three possible degradation pathways and by considering the experimental characterizations discussed above.

A. Photophysical Measurements

Inverted BDB-TF:Y6 OSCs were fabricated in an inert argon glove box by following the procedure outlined in a previous study (Fig. 1a,b), see Supporting Sections 1, 2 for details.²⁴ An active layer thickness of 120 nm was used to optimize the performance of pristine cells that were measured in the same glove box. Typical OSCs (area = 0.0625 cm²) show PCEs of greater than 16% (Fig. 1c) with a champion device delivering a PCE of 17.3%, an open circuit voltage (V_{oc}) of 0.81 V, a short-circuit current density (J_{sc}) of 18.39 mA/cm², and a fill factor (FF) of 73.4%. Pristine OSCs were then removed to ambient conditions and exposed to AM 1.5G, 100 mW cm⁻², and the current-voltage characteristics were again measured in the glove box

by increasing the exposure durations in incremental steps of 5 minutes (Fig. 1c). Most of the loss in PCE comes from decreased J_{SC} and FF while V_{OC} is relatively unchanged. The total integrated photocurrent from external quantum efficiency (EQE) measured in a glove box matches the J_{SC} of OSCs from J - V characteristics within 95% (Fig. 1d) while the residual mismatch is likely attributable to the continued slow degradation during the interval between the two measurements.

To understand the effect of contacts on the degradation process, we measured current-density-voltage (J - V) characteristics of pristine and degraded OSCs in the dark. Evolution of device performance metrics with exposure time is shown in Supporting Fig. S1. Figure 1e shows representative curves of a pristine device (PCE = 17.3%) at temperatures ranging from 295 to 140 K for IVT analysis (Supporting Section 3). All optoelectronic measurements in this and the next section were conducted on three different devices showing qualitatively similar behavior. To determine the physical processes involved in dark characteristics we fitted the J - V curves to the general Shockley diode equation (1),

$$J = \frac{R_p}{R_p + R_s} \cdot J_0 \left(\exp \left(\frac{e(V - J R_s)}{n_0 k_B T} \right) - 1 \right) + \frac{V}{R_p} + J_{SC}, \quad (1)$$

where J , V , k_B , and T are device current density, voltage, Boltzmann constant, and temperature, respectively;^{50,51} R_p and R_s are shunt and series resistances, respectively; and n_0 and J_0 are diode ideality factor and reverse saturation current, respectively. The data were fit numerically to eq. (1) (solid lines in Fig. 1e) giving excellent fits for all temperatures. Supporting Fig. S2 shows IVT characteristics and diode model fits of the same cells after PCE degradation from 17.0% to 11.1% and 5.0%. Note that while we focus on IVT characteristics primarily up to 1.0 V, for completeness we also measured devices up to 1.5 V and then extracted the series resistance (R_s) by fitting the data to eq. (1), finding that R_s remains nearly constant (Supporting Fig. S3). To further demonstrate the robustness of this fitting of the Shockley diode model, we used the Hegedus-Shafarman method⁵² to extract R_s at higher voltages (Supporting Fig. S4). Both methods give similar values of series resistance, 1.14–1.38 $\Omega \cdot \text{cm}^2$, which is 18.24–22.24 Ω for the current cells having an area of 6.25 mm^2 . These values are similar to those extracted from impedance measurements ($\approx 25 \Omega$), as discussed below. Furthermore, both methods yield a similar reverse saturation current (J_0) when fit in the low bias range and the extracted ideality factor is less than 2.0 in all cases.

Since the present model does not make any assumptions about the physical processes in charge transport, we first analyze the temperature dependence of the fit parameters to gain further insight. We find that the ideality factor n_0 for **PBDB-TF:Y6** BHJ diodes to be less than 2 at room temperature for all the devices and only becomes greater than 2 at lower temperatures following a well-established behavior in semiconductor diodes (Supporting Fig. S5). The temperature dependence of n_0 in OSCs has been reported and can be attributed to three factors: (i) band gap variation in low temperatures, (ii) interfacial recombination temperature dependence, and (iii) increased tunneling processes at low temperatures that do not pose an upper bound of 2 for n .^{52–55} Also, note that an ideal Shockley equation for the diode does not include

series or shunt resistance. The generalized Shockley eq. (1) has been extensively used to fit the temperature dependence of OPV IV curves in the dark and under illumination despite being judged “very non-ideal”.^{51,53}

Here, we note that the degradation process does not significantly affect the temperature dependence of n_0 (<10%), thus, ruling out large changes in the effective bandgap. In contrast, the fitted value of J_0 falls by four orders of magnitude from 1.37×10^{-11} to 2.23×10^{-15} A on lowering the temperature from 295 to 150 K, which might be ascribed to thermal activation across the mobility gap. However, estimation of the mobility gap from an Arrhenius-type plot of $J_0 \cdot T^{-2}$ vs T gives unreasonable values due to the rather small R_p varying from 4.47 to 17.62 M Ω over the same temperature range and makes the cell ‘leaky’ even at low temperatures.⁵¹ The model fits better at relatively large voltages ($V > 0.5$ V) where R_s dominates and thus, the extracted temperature dependence is analyzed using the eq. (2):

$$R_s = R_{s0} \exp \left(\frac{E_{rs} - \alpha \sqrt{V/d}}{k_B T} \right) \quad (2)$$

where d is the thickness of the active layer, E_{rs} is the activation energy of the series resistance, and R_{s0} is a constant prefactor.⁵¹ The barrier-lowering constant α is obtained from $\alpha = \sqrt{e^3 / \pi \epsilon_s}$, where e is the fundamental electronic charge and ϵ_s is the dielectric constant of the active layer. We obtain $\epsilon_s = 2.5$ for the **PBDB-TF:Y6** blend from capacitance-voltage measurements at room temperature from fully depleted OSCs (i.e., geometrical capacitance), and the extracted value of ϵ_s is comparable to that of blends from other NFAs (≈ 3) and **Y6** (≈ 3.5 – 3.74) reported in the literature.^{56–58} This underestimation may reflect uncertainty in thickness, roughness, and dielectric properties of **PBDB-TF**, and interfaces.

The temperature dependence of R_s is critical for fitting at large voltages and assuming a constant R_s results in poor agreement with the fits. The flattened J - V curves suggest a barrier lowering either from the Schottky effect at the contacts or the Poole-Frenkel effect in the bulk of the active layer. First, we extract $E_{rs} = 0.48$ eV (taking $\epsilon_s = 3.74$) for the undegraded cell and E_{rs} value changes by only 3% upon PCE degradation from 17.3 to 5% (Fig. 1f). Second, we obtain the lowest possible current density of 4.34 $\text{mA} \cdot \text{cm}^{-2}$ at 295 K from Schottky barrier lowering using $A_0 T^2 \exp(-E_{rs}/k_B T)$, where A_0 is the Richardson constant (120 $\text{A} \cdot \text{cm}^{-2} \cdot \text{K}^{-2}$). Since this value is less than the measured current density of 6.04 $\text{mA} \cdot \text{cm}^{-2}$ at 1 V, either the Schottky or Poole-Frenkel effect can explain the diode behavior.⁵¹ Therefore, the series resistance arises either from the contact resistance between the blend and charge transport layer or charge

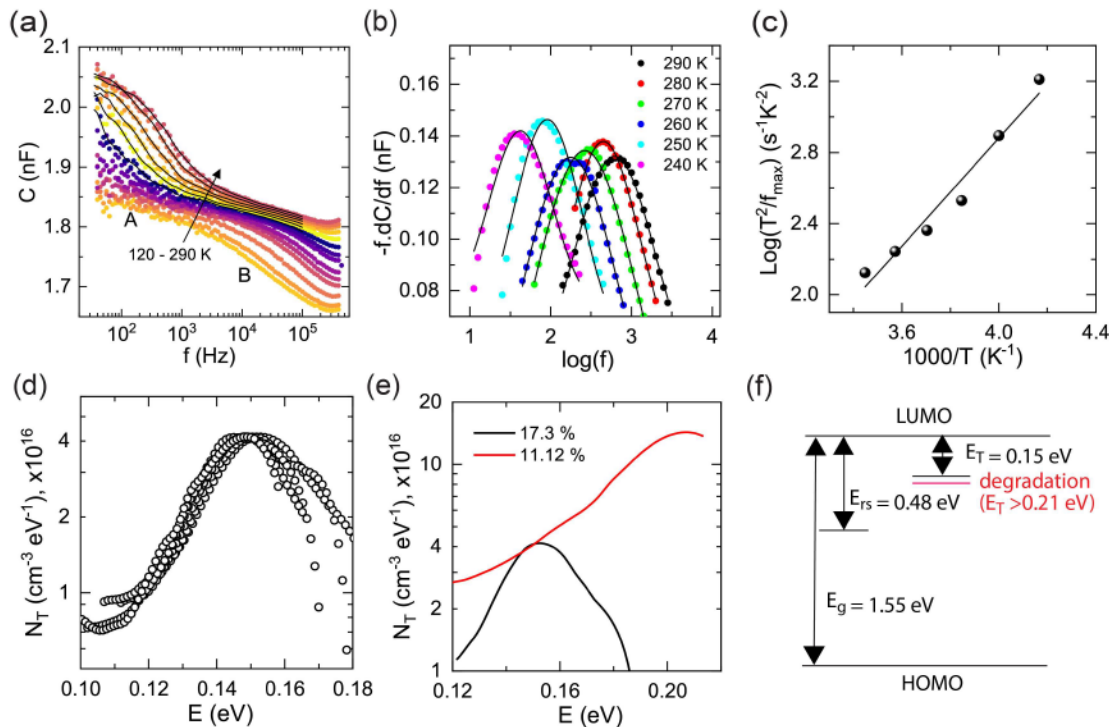


Figure 2. (a) Capacitance-frequency (C - f) characteristics of a pristine **PBDB-TF:Y6** solar cell (PCE = 17.3%) at varying temperatures from 120–290 K. The A and B regions show two 'knees' in C - f curves. Solid lines show the smoothed curve in region A. (b) Plot of $-f.dC/df$ versus $\log(f)$ for different temperatures corresponding to region A of C - f plots for the pristine cell in (a). Solid lines show fits to Gaussian functions. (c) Plot of $\text{Log}(T^2/f_{\text{max}})$ vs $1/T$ to extract the attempt frequency ν_{00} and the energy E_T for the dominant trap state using the thermal admittance spectroscopy (TAS) method. (d) Plot of the 'collapsed' density of trap states (N_T) as a function of energy from LUMO of the **Y6** molecule. (e) Comparison of energy dispersion of N_T for the pristine and the degraded cell. (f) Schematic of the energy gap ($E_g = 1.55$ eV), activation energy in the charge transport layer ($E_{rs} = 0.48$ eV), and trap energy level ($E_T = 0.15$ eV) that changed to ~ 0.21 eV after degradation.

trapping within the bulk of the solar cell. In either case, the activation energy does not change with PCE degradation. This suggests these deep traps at the contact regions or in the BHJ only begin to emerge in the last stages of degradation of these NFA-based OSCs and most of the initial PCE degradation comes from other factors. To conclude, dc-based IVT measurements revealed deep traps in the charge transport layer that do not change significantly upon rapid PCE degradation from fresh cells. Therefore, in the following, we employ impedance-based methods to probe shallow trap states within the BHJ to understand the mechanism of initial PCE degradation of OSCs.

B. Shallow Charge Trap Energetics

We next employed TAS analysis of **PBDB-TF:Y6** cells to further investigate degradation effects within the BHJ blend.^{59–65} Thus, we quantify the number, energy, and attempt frequency of the trap states in the pristine blend and then track their evolution with degradation. OSC frequency- and temperature-dependent capacitance (C_f) was measured at an applied DC voltage of 0.0 V using AC modulation of 50 mV over temperatures ranging from 295 to 120 K (Fig. 2a). First, the series resistance R_s , extracted from

impedance at 25°C, shows a significant increase from 25.3 to 56.8 Ω (1.58 to 3.55 $\Omega\text{-cm}^2$) when the PCE falls from 14.1 to 8.0% and increases more dramatically to 257 Ω (16.06 $\Omega\text{-cm}^2$) at the lowest measured PCE value of 5.9% (Supporting Fig. S6). The capacitance step in C - f plots at low frequencies (40 Hz–1 kHz, region A in Fig. 2a) is indicative of trap states in the bandgap. Thus, the variation in the inflection point of the capacitance step with temperature can be utilized to reconstruct the density of states and energy levels of the trap states.⁶¹ Note that the capacitance further decreases at higher frequencies (10–100 kHz, region B in Fig. 2a) which is not related to the trap states but is an artifact of the RC model, as explained in Supporting Fig. S7.⁶⁶ We take the numerical derivative of the data $(-f) \frac{dC}{df}$ in region A after smoothing the dataset at low frequencies (<100 Hz). The angular resonance frequency from the peak in $(-f) \frac{dC}{df}$ vs $\log(f)$ plots is given by $w = 2\nu_0 \exp(-\Delta E_T/k_B T)$, where ν_0 is the angular attempt frequency and ΔE_T is trap activation energy. We include temperature dependence of the attempt frequency, $\nu_0 = \nu_{00} T^2$ where ν_{00} is reduced attempt frequency.⁶⁰ The peaks in the

data in Fig. 2b are fit to Gaussian functions and the mean values are used to obtain an Arrhenius-type plot in Fig. 2c which yields $\nu_{00} \approx 4.92 \times 10^3 \text{ s}^{-1}\text{K}^{-2}$. For comparison, the room temperature attempt frequency of the pristine **PBDB-TF:Y6** cell $\nu_0 \approx 4.28 \times 10^8 \text{ Hz}$ is smaller than that in inorganic thin film solar cells ($6.2 \times 10^{11} - 10^{12} \text{ Hz}$),⁶¹ inorganic nanocrystal solar cells ($\approx 10^{10} \text{ Hz}$),⁶⁰ and organic-inorganic perovskite solar cells ($1.35 \times 10^9 \text{ Hz}$).⁵⁹ The smaller **PBDB-TF:Y6** attempt frequency likely reflects the relatively modest delocalization in π -stacked nanocrystals of **Y6** molecules, evident in the single-crystal x-ray diffraction. The energy and the density of the trap state are calculated from eqs. (3) and (4) where A is the area of cells,

$$E = k_B T \log \left(\frac{2\nu_{00} T^2}{2\pi f} \right) \quad (3)$$

$$N_T = \frac{V_{bi}}{AW k_B T} f \frac{dC(f)}{df} \quad (4)$$

W is the depletion width that is taken to be equal to the thickness of the active layer, and V_{bi} is the built-in voltage in pristine OSCs that is extracted to be 0.77 V at 295 K from Supporting Fig. S2a. Following these coordinate transformations, we see that all the curves from Fig. 2b collapse to a single curve in Fig. 2d yielding a maximum density of trap states of $4.16 \times 10^{16} \text{ cm}^{-3}\text{eV}^{-1}$ at $E_T = 0.15 \text{ eV}$ below the **Y6** LUMO. Such a charge trap density in pristine **Y6** is not unexpected since organic crystals typically show a broad Gaussian-like density of tail states spectrum originating from defects, grain boundaries, and other sources of heterogeneities. Recently, energy-resolved electrochemical impedance spectroscopy (ER-EIS) of pristine **PBDB-TF:Y6** solar cells revealed a density of trap states that is three orders of magnitude larger than the present values. It is reasonable that the solution-based ER-EIS measurements may have introduced extrinsic disorder that increased the trap state density.⁶⁷ Thus, taking the significantly lower density of trap states in the present TAS analysis of high-PCE pristine cells as a control implies the detection of additional trap states arising from initial degradation. TAS was next repeated on the same device after degradation to PCE = 11.1%, and the corresponding CfT plots are shown in Supporting Fig. S8. The knee of the capacitance modulation shifts towards lower frequencies and so the temperature was further increased to 340 K to bring the inflection point within the measurement bandwidth. The low-frequency capacitance also increases by 1.5-fold and the resulting density of states shows a peak of $4.16 \times 10^{16} \text{ cm}^{-3}\text{eV}^{-1}$ at $E_T = 0.21 \text{ eV}$ below the **Y6** LUMO (Fig. 2e-f). Further cell degradation below a PCE of 11% results in shifts in the knees of the CfT curves to frequencies below 40 Hz where increased noise of the impedance analyzer significantly precludes the extraction of the trap density of states (Supporting Fig. S8).

To investigate the optical signatures of the degraded molecules, we performed optical absorption spectroscopy of neat **Y6**, neat **PBDB-TF**, and **PBDB-TF:Y6** blend films cast on ZnO/ITO substrates to

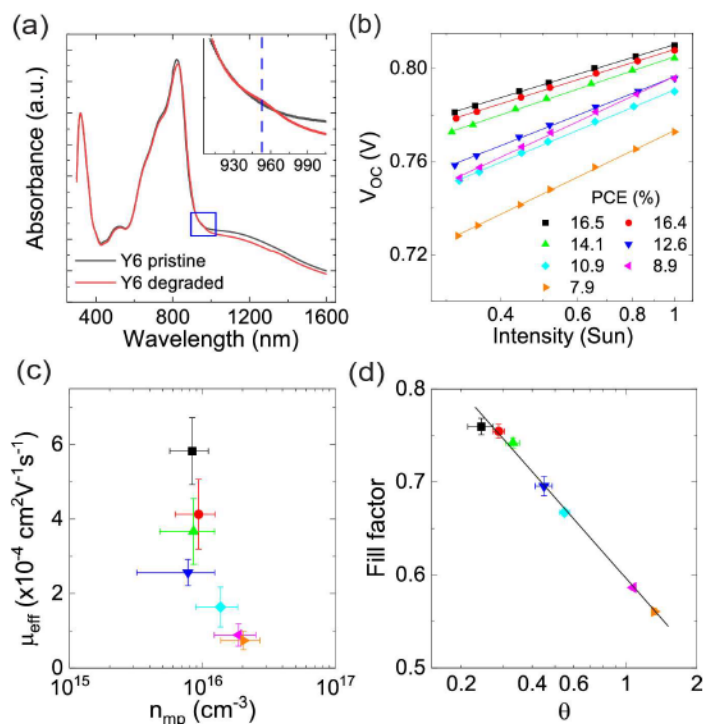


Figure 3. (a) Optical absorbance of a neat **Y6** film spin-coated on ZnO/ITO before (pristine) and after exposure (degraded) to solar illumination for 30 min in ambient. The inset shows zoomed-in data from the blue rectangle showing the emergence of a new feature at $\approx 952 \text{ nm}$ on degradation. (b) Plot of open circuit voltage (V_{oc}) as a function of illumination intensity at different degrees of **PBDB-TF:Y6** solar cell degradation. The legend corresponds to plots b-d. (c) A plot of effective carrier mobility (μ_{eff}) versus charge carrier density at maximum power point (n_{mp}) extracted from IPDA data at different stages of degradation. (d) Plot of fill factor versus competition factor at different stages of degradation. The solid line is a guide to the eye.

simulate the photo-induced degradation environment of the OSCs. The spectra were collected before (pristine) and after (degraded) exposing the films to solar illumination for 30 min in ambient conditions (Fig. 3a and Supporting Section 4, Fig. S9). Overall, all films show minor decreases in characteristic peaks after degradation, however, neat **Y6** and **PBDB-TF:Y6** blend films also exhibit the emergence of a new absorbance feature at 952 nm ($\approx 1.3 \text{ eV}$) after degradation. Surprisingly, this peak lies $\approx 0.25 \text{ eV}$ below the **Y6** LUMO, matching the peak location of degraded **Y6** extracted from TAS analysis. However, the peak intensity is small which, compared with minor changes in other characteristic peaks after degradation, suggests that the molar fraction of degraded **Y6** molecules is very small ($< 1\%$). Nevertheless, this optical observation provides a direct spectral signature of degraded **Y6** molecules that matches the TAS trap state energy. Note that neat **PBDB-TF** and **Y6** films show an 8% and 2.5% decline in the peak absorptions at 571 nm and 840 nm , respectively, during degradation. Note also that the **PBDB-TF** peak at 1150 nm does not significantly contribute to the OSC performance since the EQE is less than 1% in that regime (Fig. 1d). Thus, the neat

PBDB-TF film shows a somewhat greater decline in absorption than Y6, and these changes are well-represented in the blend optical absorption spectra. While the reduction of net photon absorption in degraded films might decrease the photocurrent in proportion, it is not the main contributor to PCE reduction in the degraded devices since the majority of the photocurrent loss in OSCs comes from increased photocarrier recombination and decreased charge generation processes that are affected by the electronic structure and blend morphology.³⁻⁷ Thus, we have limited our analysis of the UV-Vis spectra to highlight the emergence of the new feature in the Y6 spectra. To conclude, the TAS and UV-vis analyses provide new insight beyond IVT into the evolution of charge traps in the BHJ during initial OSC degradation. However, these do not provide information on the charge transport and recombination dynamics in functional OSCs under illumination. In the following, we present an *in-situ* measurement method to directly correlate PCE degradation with mobility and recombination coefficient while the cells are being operated at maximum power point.

C. Integrated Photocurrent Analysis

Here, *in-situ* IPDA measurements of PBDB-TF:Y6 cells at different stages of degradation (Supporting Section 5) were next conducted. The OSCs were degraded in a controlled manner by exposing the cells to AM-1.5G (100 mW·cm⁻²) illumination for varying durations of 2 to 30 min and then, *J-V* and IPDA measurements were performed by bringing the cells into the glove box after each degradation step as PCE fell from 16.5 to 7.9%. First, V_{oc} was measured as a function of illumination intensity (I) and the result is shown in Fig. 3b. The slope of V_{oc} versus $\log(I)$ is ideally expected to be $k_B T/e$ (25 mV at room temperature) and $2k_B T/e$ for bimolecular recombination and monomolecular recombination, respectively.^{31, 68} However, space charge effects and other OSC non-idealities can yield larger values.⁶⁹ In pristine PBDB-TF:Y6 cells (PCE = 16.5%) we obtain a slope of 57 mV/decade that gradually increases to 87 mV/decade in degraded cells with PCE = 7.9% (Fig. 3b and Supporting Fig. S10a). Although both values are larger than $2k_B T/e$, an increase in the slope by 30 mV/decade suggests significantly increased monomolecular recombination from the increased density of trap states in the degraded cells.

From the IPDA data, the bimolecular recombination coefficient (k_{br}) is seen to fluctuate within instrumental noise for PCE changes from 16.5 to 12.6% and only then falls with the PCE degradation from 10.9 to 7.9%. This can be explained by dominant monomolecular recombination scavengers that reduce the fraction of photocarriers participating in the bimolecular processes (Supporting Fig. S10b). The reverse bias photocurrent shows only a slight reduction in the saturation behavior upon PCE degradation from 14.1 to 7.9%, again confirming minor changes in bimolecular recombination (Supporting Fig. S11). Note that this is in stark contrast to NFA-based OSCs with acceptors having end groups of varying degrees of fluorination where differences in PCE are inversely correlated with the IPDA-derived bimolecular recombination coefficient.^{24, 28} Therefore, the PCE reduction by Y6 degradation does not follow the same morphology-dominated PCE loss mechanisms as NFAs having different end groups

that strongly affect blend morphology.^{24, 27} Instead, here the mean electron mobility falls more rapidly with degradation, by up to six-fold in PCE = 7.9% cells (Fig. 3c). Creation of new deep charge traps from degraded Y6 molecules is expected to strongly affect charge transport in Y6 nanocrystals even if the overall BHJ blend morphology is largely unaffected. Interestingly, the free charge carrier density and chemical capacitance at the maximum power point (n_{mp}) does not increase significantly with degradation (Fig. 3c and Supporting Fig. S12). Thus, acceptor degradation affects the OSC performance through two major physical processes: increased monomolecular recombination and decreased electron mobility. The competition factor (θ) is defined as the ratio of the recombination rate to the charge extraction rate and captures the relative contributions from the two competing effects. In OSCs, FF scales inversely with θ and such a scaling relation has been observed in blends based on a wide range of functionalized NFAs.^{24, 27-29, 70} Here, the PBDB-TF:Y6 cell degradation scales with FF , almost linearly with $\log(\theta)$ (Fig. 3d), suggesting poor charge extraction and increased recombination in degraded cells. Overall, the electrical measurements have quantified trap densities and correlated OSC degradation with steady-state competing processes of charge extraction and recombination. However, electrical measurements do not give insight into non-steady state photoexcited carrier dynamics that can be correlated with degradation at the molecular level. Ultrafast pump-probe spectroscopy has proven to be a powerful technique to understand excited state dynamics in OSCs and thus, we next employ this method to understand the effects of degradation.

D. Excited-State Dynamics

The relationship between PCE degradation and excited-state dynamics for PBDB-TF:Y6 blends and neat Y6 films was investigated using transient absorption (TA) spectroscopy by exciting at 800 nm with a 20 μ J cm⁻² pulse (Supporting Section 6, Fig. 4, and Figs. S13-S15). In the pristine blend, prominent excited-state absorption (ESA) bands appear at 690 and 760 nm (PBDB-TF) and 910 and 1500 nm (Y6) along with ground-state bleach (GSB) at 570 and 630 nm (PBDB-TF) and 730 and 800 nm (Y6). Following rapid (< 1 ps) hole injection, geminate recombination occurs with a lifetime of 8 ps, followed by slower recombination between 300 ps and 150 ns (Supporting Table S1) with minimal spectral evolution. These longer-lived populations correspond to free carriers undergoing bimolecular recombination.⁷¹

For a direct comparison, the evolution-associated spectra of the pristine and degraded PBDB-TF:Y6 blends are shown in Supporting Fig. S13. The first spectral component (state A) shows the bleaching of Y6 (650-900 nm), but also some contribution from the bleaching of the PBDB-TF donor in the 500-650 nm region that indicates a contribution from ultrafast hole transfer. These features appear along with some excited-state absorption from the Y6 Frenkel exciton that diminishes with time in the 850-1000 nm and 1100-1400 nm regions.³⁰ Similar excited-state absorptions are also observed in the neat pristine Y6 films (Supporting Fig. S14). The spectrum of state B resembles that of state A but with a lower amplitude of the Frenkel exciton features. These two states show distortion of the Y6 bleach below 800 nm due to contributions from the charge carrier

absorptions and both show the hole injection process, with fast and slow contributions from optimal (A) and sub-optimal (B) donor-acceptor packing in the film, respectively. Neither of these states is dramatically affected by the degradation process, as their spectra and kinetics are very similar, although the sub-optimal charge injection is slightly faster following UV exposure of the film.

The spectrum of state E is also similar to that of C and D and can be assigned to free carriers that decay via non-geminate recombination based on the minimal spectral evolution and much longer recombination time (~ 100 ns). The decay of state E is moderately accelerated by the degradation process. The final state is unaffected by the UV irradiation; this may be a thermal artifact or photoproduct state, but it is very low in amplitude, and we,

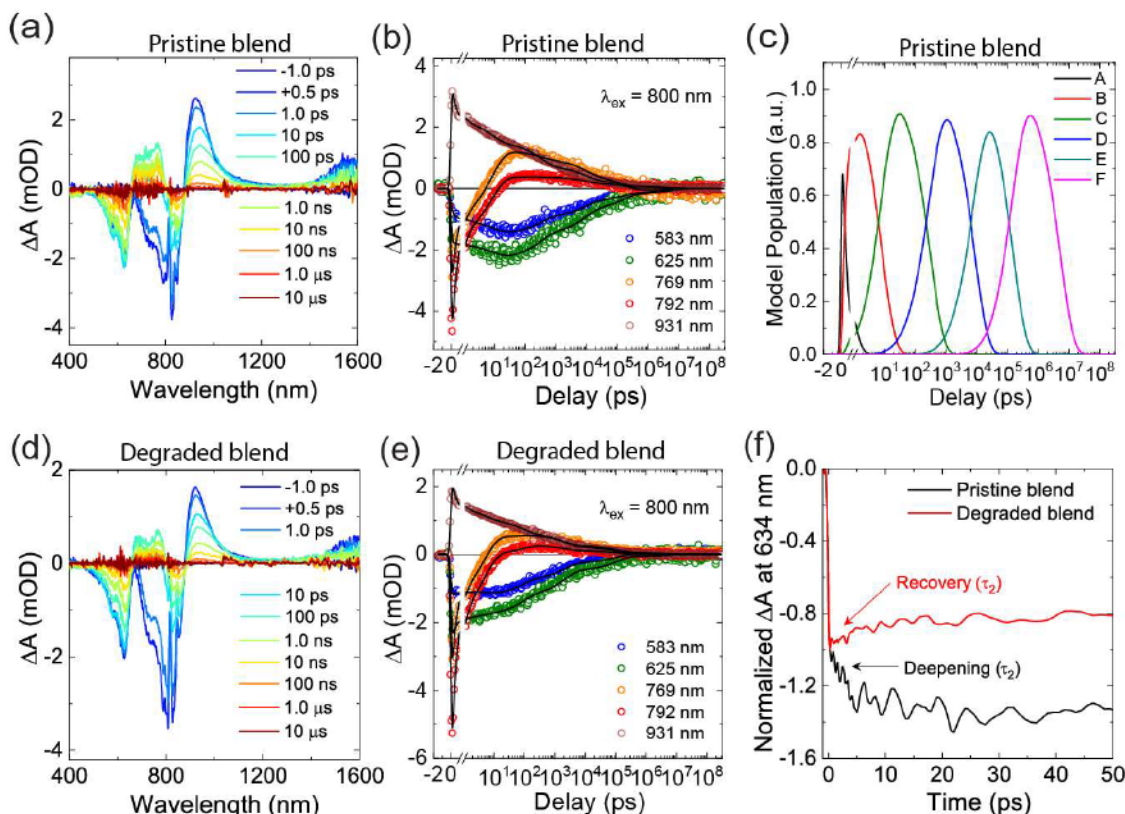


Figure 4. (a) Transient absorption (TA) spectra of a pristine **PBDB-TF:Y6** blend film taken at different delay times when excited at 800 nm (20 mJ·cm⁻²). (b) Corresponding time-resolved differential absorption (ΔA) at indicated wavelengths (symbols). The solid lines show model fits from global analysis. (c) Model population dynamics of different species (A-F) in the pristine blend. (d), (e) TA spectra and time-resolved ΔA of the same **PBDB-TF:Y6** blend film after degradation. (f) A comparison of bleach kinetics shows the deepening of the bleach in a degraded blend over a few picoseconds. The instrument response function is 300 fs.

The spectra of the next two states (C, D) represent the charge carriers, with the polymer bleach in the 500-650 nm range, Y6 bleach in the 800-900 nm range, and the excited-state absorption of the carriers between 680-800 nm and 900-1000 nm.⁷¹ Additionally, at longer times there may also be some contribution from the Y6 triplet-triplet absorption beyond 1400 nm.⁷² These spectra decay with time constants ranging from ~ 100 ps (state C) to ~ 10 ns (state D) with minimal spectral evolution. From their short decay times, the populations associated with these spectra likely decay via geminate recombination, as the excitons do not have a sufficiently long lifetime to effectively dissociate and diffuse away. Both time constants are strongly affected by the degradation process, with each being accelerated by a factor of $\sim 4\times$. This likely reflects an increase in local trap states and changes in morphology that limit carrier lifetime.

therefore, forego interpretation.

We emphasize here that the spectral signatures of the degraded blend film (Fig. 4d,e) and the hole transfer rate are changed, while the recombination kinetics are dramatically affected (Fig. 4f). Each recombination step captured by the sequential kinetic model is accelerated, with the fastest (5 ps) and slowest (153 ns) decays increasing by $\sim 50\%$, the intermediate processes (e.g., 8.9 ns) accelerate by as much as a factor of $4\times$ upon degradation. This result is consistent with the loss of electron mobility and increased rate of geminate recombination discussed above, all of which will reduce the available charge collected at the electrodes thereby lowering device performance. In contrast, TA analysis of pristine Y6 films before and after degradation does not reveal conclusive trends as in the blend data (Supporting Figs. S14, S15). Note, this sequential

model is an oversimplification and does not account for many-body effects such as singlet-singlet- and triplet-triplet annihilation, both of which are bimolecular in nature.^{73,74} So far, we have focused on the evolution of electronic structure and charge dynamics upon OSC PCE degradation. A comprehensive picture of degradation can only emerge by also studying the structural and morphological evolution of the BHJ during degradation. X-ray measurements have been widely used in the structural analysis of NFA BHJs and we next leverage that to elucidate microstructural changes in crystalline OSC phases upon PCE degradation.

E. X-ray Structural Analysis

GIWAXS was employed to evaluate microstructural changes of neat **Y6**, neat **PBDB-TF**, and blend (**PBDB-TF:Y6**) films arising from photodegradation. Neat and blend films were prepared on Si substrates using identical fabrication procedures as described for OSC device fabrication (see Supporting Section 7). Note that GIWAXS measurements required the fabrication of films on Si substrates rather than on ZnO-coated ITO substrates to avoid background scattering that would complicate the NFA GIWAXS analysis. Note that degradation has been shown to occur in the presence of O₂ even without ZnO, e.g., in conventional OSCs with ITO substrates coated with **PEDOT:PSS**.⁴⁶ Although the interface between the active layer and the charge transport layer plays a significant role in the degradation of OPV performance,⁷⁵ photodegradation within the polymer/NFA blends can occur within 15 minutes in the absence of the ZnO ETL, and without significant disruption of the blend film morphology/microstructure, indicating that more nuanced and subtle structural changes lead to compromised device metrics.^{44-46,76} The primary reactive species in such instances are known to be superoxide and hydroxyl radicals generated from photolytic reactions with ambient moisture and O₂.^{44-46,77,78}

Pristine films (neat and blend) were maintained under an inert environment before the GIWAXS measurements, while degraded films were prepared by exposing them to the same solar illumination under ambient conditions for 30 min. GIWAXS diffraction patterns and related line-cut profiles for the out-of-plane (OOP) and in-plane (IP) reflections are provided in Fig. 5, Supporting Figs. S16, S17, and Table S2. For all films, lamellar spacings (reflection = 100)/ π - π distances (reflection = 010) and their corresponding crystal coherence lengths (CCLs) were determined from the IP/OOP reflections, respectively. For pristine (undegraded) neat **Y6**, neat **PBDB-TF**, and **PBDB-TF:Y6** blend films, the diffraction patterns and

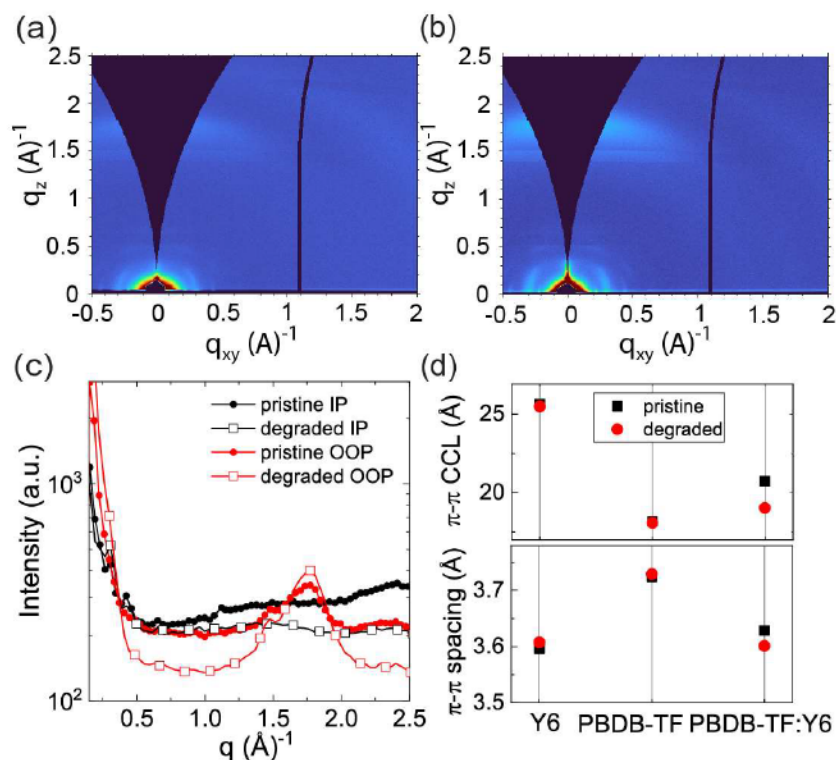


Figure 5. (a), (b) GIWAXS diffraction patterns of pristine and degraded **PBDB-TF:Y6** blends, respectively. (c) Line cuts along in-plane (IP) and out-of-plane (OOP) directions for pristine and degraded blend films. (d) π - π crystal coherence length (CCL) and π - π spacings for pure **Y6**, pure **PBDB-TF**, and **PBDB-TF:Y6** blend films before and after degradation.

trends for lamellar spacing (24.29/24.50/21.64 Å) and π - π distances (3.60/3.72/3.63 Å) and corresponding CCL values (38.67/33.92/59.32 Å and 25.66/18.18/20.74 Å) are similar to those of previous reports.^{25,79} Photodegradation of the neat **PBDB-TF/Y6** films (Supporting Fig. S16, S17, and Table S2) induces slight changes in the lamellar spacings/CCL (23.36/41.21 Å and 23.42/33.49 Å) with no observable difference in the π - π distances/CCL (3.73/18.07 Å and 3.61/25.50 Å). The change in lamellar spacing is slightly greater for the degraded neat **PBDB-TF** films than for the degraded neat **Y6** films. These changes agree with values reported in the literature,^{25,79} and they are not observed in the blend films. Morphological changes in the blends involve additional donor-acceptor interaction features that are not present in the neat films. For the degraded **PBDB-TF:Y6** blend, the lamellar spacings/CCL (21.26/59.71 Å) and π - π distances/CCL (3.60/19.03 Å) are very similar to the pristine blend films indicating that the polymer/NFA structural changes due to photodegradation do not significantly contribute to observable changes in the morphology and microstructure, again consistent with previous reports.⁴⁴⁻⁴⁶ Rather, the photodegradation of **PBDB-TF:Y6** blends can be attributed to a photo-oxidation process whereby oxidation of the exocyclic vinyl groups leads to epoxide formation and the subsequent degradation of the **Y6** end-group, as reported for other NFAs.⁴⁹ While complete scission of the **Y6** end-group or scission of the dicyanomethylene group is expected to create catastrophic disruption of the 3D structure, these scenarios are inconsistent with

GIWAXS analysis (Fig. 5).²⁹ However, a reduction in conjugation length due to vinyl oxidation and the resulting changes in electronic structure could easily decrease electron mobility and increase recombination rates without disrupting the overall morphology of the PBDB-TF:Y6 BHJ. Thus, the X-ray measurements reveal that PCE degradation is not accompanied by significant structural changes in the BHJ morphology and that is consistent with the aforementioned observations that only a small mole fraction (<1%) of degraded NFA molecules is needed to reduce PCE by 50% upon degradation. Finally, we introduce a computational analysis to develop a complete picture of chemical degradation pathways that is consistent with the experimental analyses discussed so far.

F. Molecular and Electronic Structural Analysis

To gain a molecular and electronic understanding of the PCE degradation process, we performed density functional-based tight binding (DFTB) calculations to generate possible Y6 degradation pathways (Supporting Section 8). We considered and optimized the Y6 and the structures (or fragments) of its three plausible UV-induced degradations in the calculations. The three pathways considered represent the three functional groups of Y6 most likely to be reactive to a free radical.^{36, 38, 39, 46, 49} The first is the end group-core linking the vinyl group oxidation (Fr1), as shown in Fig. 6a. The second is at that same position having a bond scission leading to end group scission from the core (Fr2) (Fig. 6a). The third degradation pathway considered is dicyanomethylene end group scission (Fr3), as shown in Fig. 6a. Further details of the three degraded structures are shown in Supporting Fig. S18. We additionally examined the doubly degraded fragments Fr1d, Fr2d, and Fr3d by considering degradation reactions on both acceptor end groups. Although two reactions on the same Y6 molecule would be statistically unlikely to happen under the solar fluxes considered here, we used the doubly reacted Y6 structures as a comparison tool.

From each degraded structure we selected frontier molecular orbitals (FMOs) of each molecule for comparison (Figs. 6b, 7a,b and Supporting Table S3, Figs. S19-S25). Note that only the LUMO energy levels of Fr1 (-4.46 eV) have much lower energy levels versus the Y6 LUMO (-4.29 eV) (Fig. 6b). Furthermore, the HOMO energy levels shift upwards in all the fragments signifying the destabilization of the π orbitals (Supporting Figs. S19-S25). This lowered LUMO energy level and a relatively small change in HOMO corresponds to the experimental optical absorption spectrum where redshift is observed after the Y6 degradation and is due to the

formation of hydrogen bonds around the hydroxyl group after vinyl oxidation, as discussed later.

We also computed FMO of the singly and doubly charged anionic Fr¹⁻ and Fr²⁻ and have stabilized the corresponding anions by incorporating Zn²⁺ cations in the vicinity, as shown in Fig. 7a. From our characterizations of the PBDB-TF:Y6 blend films (*vide supra*), we detail that minimal disruptions to the morphology and crystal structure can still contain deep trap states emerging due to photo-oxidation. The anions constructed here are entirely consistent with the ZnO acting as a photo-catalytic center for Y6 degradation, even away from the ZnO interface. The anionic fragments, stabilized with Zn²⁺, shown in Fig. 7a, offer a plausible Y6 degradation pathway

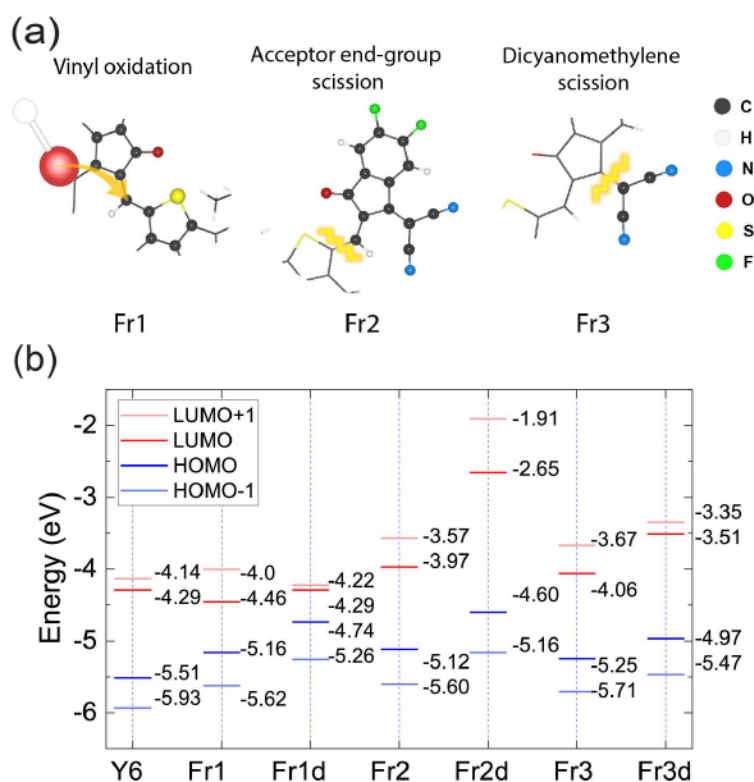


Figure 6. (a) Chemical structures of three types of possible single fragmentation products of a degraded Y6 molecule. Single (double) fragmentation via vinyl oxidation, acceptor end-group scission, and dicyanomethylene scission are labelled as Fr1, Fr2, and Fr3 (Fr1d, Fr2d, and Fr3d), respectively. The full chemical structures of all variations of the degraded Y6 molecules are shown in Supporting Fig. S18. (b) Energy levels of frontier molecular orbitals (HOMO-1, HOMO, LUMO, and LUMO+1) on pristine Y6 and degraded products after six kinds of degradation on Y6.

within the BHJ active layer. These anions were constructed by removing each H atom connected to the N atom in the dicyanomethylene group, and neutral molecules with the Zn²⁺ cation were constructed after additional dehydrogenation of the hydroxyl group. The Fr¹⁻ anion with one additional electron shows unfavourable FMO energetics of about 2 eV compared to Fr¹. The Fr¹⁻ anion with two additional electrons has even more elevated FMO energies of about 4 eV versus Fr¹ because the electrons populate

antibonding molecular orbitals. In the case of the neutral molecule paired with a Zn^{2+} cation, the molecule shows an overall tendency of much higher FMO energy levels versus Fr^{1-} (Fig. 7b). The molecule derived from **Fr1d** shows lower energy levels in the occupied molecular orbitals including the HOMO, with the LUMO and LUMO+1 energy levels even higher than those of original **Fr1d**. Therefore, anions or stabilized anions do not have lower LUMO levels compared to the charged neutral species. However, to go beyond gas-phase FMO calculations of the anion states is beyond the scope of this manuscript. This is because the anion state in the solid crystal structure requires a polaronic treatment, and an additional term in the Hamiltonian to describe the charge aggregation must be considered to obtain an exact stabilized anion state.

We next investigated the crystalline packing of the three degraded **Y6** structures to connect the molecular geometry to the generated trap states. The crystal structures were constructed by substituting the unit **Y6** molecule of the original C12/c1 crystal structure²⁴ with each **Y6** and a degraded molecule, respectively, and they were subsequently optimized to match the stacking structure (Fig. 8, Supporting Figs. S26-S30 and Table S4). We note that the doubly oxidized crystal structure of **Fr1d** was not considered because of its unstable structure when it packs in the C12/c1 crystalline phase (not shown). The total density of states (TDOS) and partial density of states (PDOS) of each of the crystal structures are compared after optimization in Fig. 8b and Supporting Figs. S31-S35.

Note that the trap energy level of the **Fr2d** crystal occurs significantly far away from the Fermi energy level and is distinct from the other structures. This is because the π -structure in the **Fr2d** crystal is significantly truncated by the elimination of two end groups. Interestingly, a well-defined trap energy level of $E_T = 0.25$ eV is observed in the **Fr1** crystal (Fig. 8b) compared to a shallow trap level of $E_T = 0.12$ eV in the pristine **Y6** crystal (Supporting Fig. S31). This significant difference between these values agrees well with TAS observed E_T measurement of 0.25 eV (vide infra; Fig. 2d-f). In contrast, the acceptor end-group and dicyanomethylene scissions either show minor evolution in the

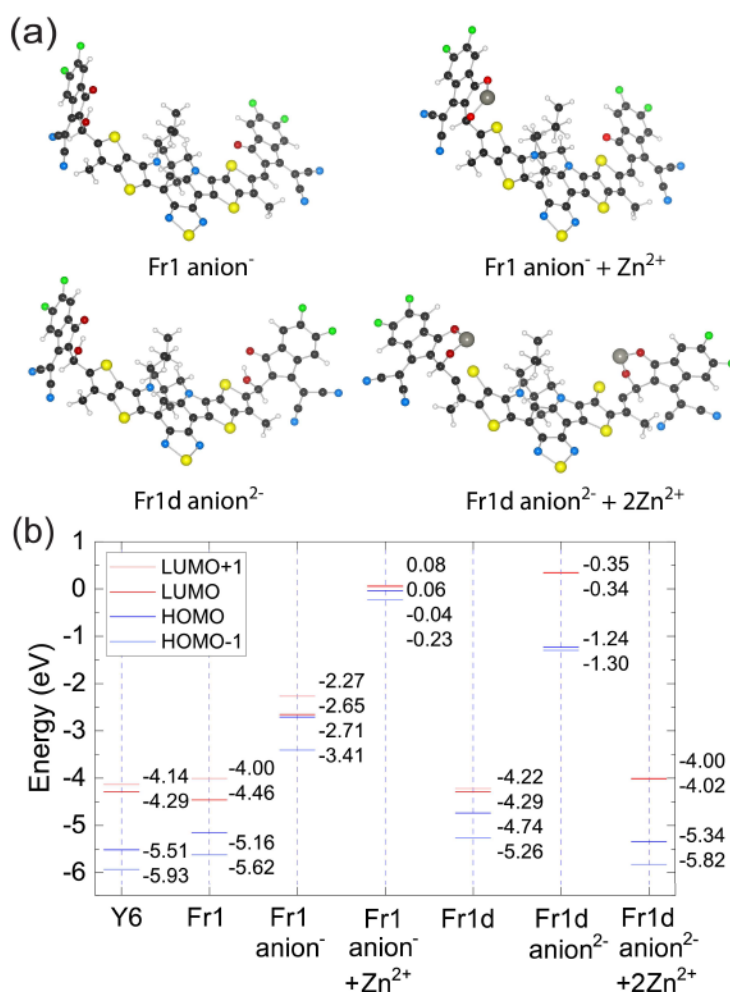


Figure 7. (a) Optimized molecular structures of the “**Fr1 anion⁻**” and “**Fr1d anion²⁻**” that are singly and doubly charged fragments, respectively. To create an anion from **Fr1** and **Fr1d**, a hydrogen atom was removed from the nitrogen atom within the dicyanomethylene group. Charges have been stabilized by Zn^{2+} in “**Fr1 anion⁻ + Zn²⁺**” and “**Fr1d anion²⁻ + 2Zn²⁺**” fragments after additional removal of the hydrogen atom from the hydroxyl group. Charges have been stabilized by Zn^{2+} in “**Fr1 anion⁻ + Zn²⁺**” and “**Fr1d anion²⁻ + 2Zn²⁺**” fragments. The atom color scheme is identical to that in Fig. 6a. Zn^{2+} is labeled as gray. (b) Frontier molecular orbital energy levels (HOMO-1, HOMO, LUMO, and LUMO+1) of pristine **Y6** and degraded products **Fr1** and **Fr1d** after each degradation on **Y6**, depending on the charge state and the existence of Zn^{2+} . “**Fr1 anion⁻**” and “**Fr1d anion²⁻**” have -1 and -2 as total charges, respectively, and all other molecules are charge neutral.

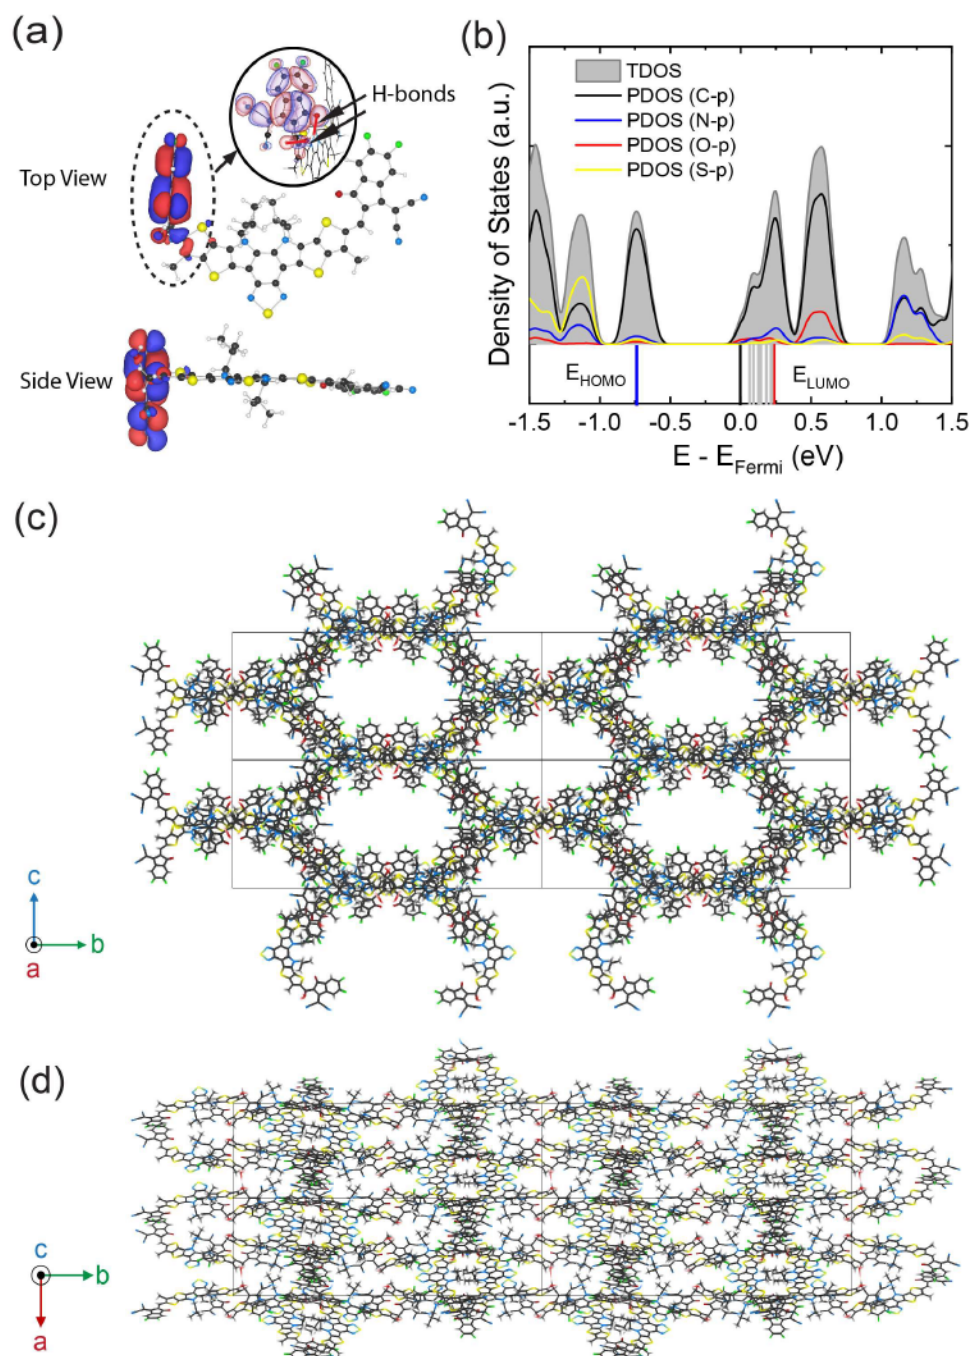


Figure 8. (a) LUMO of **Fr1** molecule after vinyl oxidation. The inset shows the formation of hydrogen bonds around the hydroxyl group. The HOMO of **Fr1** is shown in Supporting Fig. S20. (b) TDOS and PDOS (*p* orbital of carbon, nitrogen, oxygen, and sulfur) of the **Fr1** crystal structure. Energy levels of HOMO (E_{HOMO}), LUMO (E_{LUMO}), and trap energy levels are shown by blue, orange, and grey solid vertical lines below the x-axis. Energy spectra are smeared with a value of 50 meV. (c) and (d) Optimized crystal structure of **Fr1** in top and side views, respectively, based on the original pristine **Y6** crystal structure. The color scheme on each element is identical to that in Fig. 6a.

LUMO or a dramatically different TDOS profile that is inconsistent with experimental data. We find that the **Fr1** mid-gap states can be explained by the PDOS, which shows the *p* orbitals of the oxygen

causing the low-lying states in the **Fr1** crystal. These states are red-shifted toward the Fermi level compared to that of the **Y6** crystal while the LUMO energy level of **Fr1** shows strongly localized

molecular orbitals on the side where vinyl oxidation occurs (Fig. 8a). We note that these red-shifted mid-gap states are distinct from the shifted FMO energies between **Y6** and the three proposed degraded fragments.

The **Y6** degradation pathway of **Fr1** is in agreement with a recent report detailing the chemical degradation pathway in **Y6** involving breakage of conjugation with the vinyl group.⁸⁰ The vinyl group cleavage was suppressed by fluorination of the end groups and incorporation of long side chains to achieve photostability in hot (300 K) outdoor climates. The present results also agree with previous reports on an **ITIC**-based OSC where Nuclear Magnetic Resonance and Fourier Transform Infrared spectroscopies revealed vinyl oxidation as the principal mechanism of **ITIC** molecule photo-induced degradation.³⁶ As a proof-of-concept, we computed the UV/vis absorption spectra of the **Y6** and **ITIC** molecules along with the three fragments using TDDFT (Supporting Section 8) and found transition state orbitals that are consistent with the destabilization of the vinyl group (Figs. S36–41).

An *in-situ* Raman study on an **ITIC** molecule undergoing gradual degradation also suggested vinyl linkage breaking between the electron-donating core and the electron-deficient end groups.³⁹ Computational and experimental studies of other fused and non-fused NFAs (such as **IT-4F**, **PTIC**, etc.) also showed photochemical degradation at the vinyl linkage.⁴⁹ UV light can be absorbed in the ZnO bandgap of 3.37 eV, generating an electron-hole pair where the hole can initiate the desorption of neutral O₂ and the electron then becomes available to break the double bond at the vinyl linkage.³⁵ Indeed, X-ray Photoelectron Spectroscopy of degraded **PBDB-TF:Y6:PC₇₁BM** OSCs confirms the role of ZnO in the degradation mechanism. We acknowledge that degradation of the donor polymer **PBDB-TF** is likely to have a minor effect on the overall performance degradation. In ref.⁴⁴, OSCs containing fullerene (**[70]PCBM**) and non-fullerene (**ITIC**) acceptors and the same donor polymer **PBDB-T** are compared to isolate the specific role of donor polymer degradation in cell performance. **ITIC**-containing blends show a 38% decrease in PCE upon degradation compared to 9% in those with **[70]PCBM** suggesting minor effects of the donor polymer degradation on overall cell performance loss.

The present study on high-PCE **PBDB-TF:Y6** OSC degradation not only confirms earlier work on other NFA OSC compositions but goes beyond by comparing experimental and computational results, also and quantifying the effects of degradation by correlating macroscopic parameters such as PCE with microscopic parameters such as trap density of states and recombination coefficient in operating cells. Importantly we find that the overall fraction of degraded molecules can be minute and still produce a significant PCE reduction. This is consistent with two observations here. First, the optical absorption spectroscopy of degraded neat **Y6** and **PBDB-TF:Y6** blend films show the emergence of a relatively minor peak corresponding to the degraded molecule. The absorption peak cross-section can be expected to approximately scale linearly with the fraction of degraded molecules and suggests that photo-degradation involves less than 1% mole fraction. Second, both GIWAXS measurements and computations show minor changes (4.3% change

in volume and 2.5% change in lattice parameter) in morphology/metric parameters between **Y6** and **Fr1** (Supporting Tables S2, S4) and such volume-conserving degradation is consistent with vinyl oxidation but not with hypothetical routes of **Y6** end-group and dicyanomethylene scissions.⁴⁹ Such small mole fraction of degraded **Y6** molecules reducing PCE by half also suggests the long-range interaction of trap states with charge carriers. Indeed, low-mobility semiconductors typically have highly localized interactions with trap states, and therefore, the present observations are consistent with high-mobility coherent channels that are predicted in NFA nanocrystals.⁸¹

Y6 degradation in the form of **Fr1** does not lead to decomposition into two separated fragments but it weakens the bond which could lead to complete fragmentation (**Fr2**) via subsequent activation. To identify the chemical structure of decomposed **Y6** we performed matrix-assisted laser desorption/ionization time-of-flight (MALDI-ToF) measurements of degraded **Y6** films (Supporting Section 9). First, the MALDI-ToF spectra of pristine **Y6** film directly deposited onto MALDI-ToF plates by drop casting reveals a strong peak at $m/z = 1450.5$ that agrees well with the calculated value for **Y6** (Supporting Table S5 and Fig. S42). Next, **Y6** films deposited onto ZnO/ITO substrates were subjected to the same solar illumination degradation procedure as used for OSCs, and the degraded **Y6** film was deposited on a MALDI-ToF plate as a solution in 1,2-dichlorobenzene. The MALDI-ToF spectra of these films show a strong peak ($m/z = 1225.4$) assignable to **Fr2** (Supporting Table S5 and Figs. S42, S43). This feature agrees with earlier MALDI-ToF measurements on degraded **Y6**-based solar cells, however, that study was limited to correlating device metrics and proposing a chemical degradation pathway.⁴⁸ Here, in degraded cells, **Y6** and **Fr1** may decompose into **Fr2** either during the film dissolution or during the MALDI-ToF measurement that exposes the **Y6** film to UV light for molecular ionization. Therefore, subtle changes in **Y6** during initial degradation via the formation of **Fr1** should be sufficiently deleterious to decrease PCE by up to 50%. This does not eliminate the possibility of **Fr2** formation in the partially degraded OSCs although energy level calculations suggest it is less likely to form than **Fr1**. We also note that double scissions on a single molecule are expected to be extremely rare since the overall volume fraction of vinyl oxidation is small and the computed crystal structures of **Fr1d**, **Fr2d**, and **Fr3d** are not consistent with the GIWAXS experimental data (Supporting Tables S2 and S4). Note that we do not observe any of the double scission fragments in MALDI-ToF spectra of the partially degraded **Y6** (Supporting Fig. S42) and previous observations of **Fr2d** in degraded films are likely caused by a significantly greater degree of **Y6** degradation.⁸² Here, we do not consider OSCs that are degraded beyond 50% of their original PCE values.

In principle, NFA degradation could be mitigated either by using an alternative electron transport layer⁸³ or incorporating stabilizers such as dithiocarbamates or **ET18**,^{46, 84} or by passivating the ZnO layer, e.g., by using polyethylenimine or self-assembled monolayers.^{35, 46} Note that even suppressing the catalytic role of ZnO, NFA-based OSCs can degrade by other pathways due to

inherent reactivity and aggregation of **Y6** molecules, and such effects can be mitigated by designing stable end-groups (e.g., by fluorination) and/or by incorporating long side chains.^{33, 35, 44, 80, 85} While we considered a reactive NFA in the present study, practical OSCs will need to address the origins of other instabilities that may result from the donor polymer, such as the twisting of the polymer backbone.⁸⁶

Conclusions

Here we have correlated the evolution of trap density of states, mobility, and recombination dynamics with the degradation processes of high-performance **PBDB-TF:Y6** solar cells (PCE > 17%). Starting from the suggested and plausible role of the ZnO ETL layer in triggering OSC NFA degradation, we quantify the correlation between macroscopic device metrics such as PCE with microscopic processes such as trap energy and density of states, carrier mobility, and recombination rates. Two kinds of trap states are identified. The deep traps at 0.48 eV from the **Y6** molecule LUMO are from interfacial states, contribute to series resistance, and are unaffected by the OSC degradation. The density of shallow trap states at 0.15 eV from the **Y6** molecule LUMO in the BHJ rapidly increases (three-fold) with PCE degradation by 30% and shifts to a new energy level of 0.21 eV, thereby increasing monomolecular recombination and decreasing cell carrier mobility under operating conditions. The emergence of these trap states can be detected by absorption spectroscopy and a <1% fraction of degraded molecules is sufficient for severe OSC PCE performance degradation by 50%. Our experimental results and quantum calculations reveal vinyl oxidation as the putative chemical pathway of **Y6** degradation and this volume-conserving process does not affect the crystal structure significantly while revealing the emergence of a new density of states peak at 0.25 eV below the LUMO of degraded **Y6** that agrees with capacitance and optical measurements. Thus, chemical degradation of the **Y6** molecule does not affect the performance through major changes in film morphology, which had been the traditional guiding principle to design NFA molecules and end-groups, but instead affects the charge transport and extraction processes through newly developed trap states in degraded **Y6** molecules without full dissociation into separate fragments that determine the ultimate OSC performance. Such subtle changes were not evident in previous literature that mostly focused on dissociated fragments by mass spectroscopy in fully degraded cells. Thus, NFA-based stable OSC technologies would benefit from improved ETIs and mitigating vinyl oxidation by various strategies discussed earlier. Clearly, the first step in suppressing these processes is by understanding them.

Author Contributions

V. K. S. and Z. M. contributed equally. V.K.S., Z.M., A.F., T.J.M., and M.C.H. conceived the idea. G.L., F.Q. and Y.C. fabricated the solar cells. V.K.S. and Z.M. performed photophysical and trap energetics measurements and analysis. S.H. assisted in electrical data analysis. R.M.P. and D.Z. conducted GIWAXS measurements and data analysis. W.C.J. and K.L.K. performed computational analyses. R.M.Y. performed and analyzed transient absorption spectroscopy

measurements. All authors discussed the results and assisted in writing the paper.

Conflicts of interest

There are no conflicts to declare.

Acknowledgments

This work was supported by U.S. Office of Naval Research Contract #N00014-20-1-2116 (G. L.: material synthesis and characterizations), by the U.S. Department of Commerce, National Institute of Standards and Technology as part of the Center for Hierarchical Materials Design Award #70NANB19H005, and by the Northwestern University Materials Research Science and Engineering Center Award NSF DMR-1720139 (V. K. S., Z.M.: charge transport measurements). This work (IVT, TAS, and IPDA) made use of the MatCI Facility which receives support from the MRSEC Program (NSF DMR-1720139) of the Materials Research Center at Northwestern University. Transient optical spectroscopy was supported by the U. S. Department of Energy, Office of Science, Office of Basic Energy Sciences under Award DE-FG02-99ER14999 (MRW). Theory work (G.C.S.) was supported by NSF Grant CHE-2055565. This work made use of the GIANTFab core facility at Northwestern University. GIANTFab is supported by the Institute for Sustainability and Energy at Northwestern and the Office of the Vice President for Research at Northwestern. R.M.P. acknowledges support from the Intelligence Community Postdoctoral Research Fellowship Program at Northwestern University administered by Oak Ridge Institute for Science and Education (ORISE) through an interagency agreement between the U.S. Department of Energy and the Office of the Director of National Intelligence (ODNI). This work made use of the IMSERC MS facility at Northwestern University, which has received support from the Soft and Hybrid Nanotechnology Experimental (SHyNE) Resource (NSF ECCS-2025633), the State of Illinois, and the International Institute for Nanotechnology (IIN). This work also acknowledges the U.S. Department of Energy under contract no. DE-AC02-05CH11231 at the beamline 8-ID-E of the Advanced Photon Source, a U.S. Department of Energy (DOE) Office of Science User Facility operated for the DOE Office of Science by Argonne National Laboratory under Contract No. DE-AC02-06CH11357.

Notes and references

1. K. A. Mazzio and C. K. Luscombe, *Chem. Soc. Rev.*, 2015, **44**, 78-90.
2. L. Lu, T. Zheng, Q. Wu, A. M. Schneider, D. Zhao and L. Yu, *Chem Rev*, 2015, **115**, 12666-12731.
3. P. Cheng, G. Li, X. Zhan and Y. Yang, *Nature Photonics*, 2018, **12**, 131-142.
4. C. Yan, S. Barlow, Z. Wang, H. Yan, A. K. Y. Jen, S. R. Marder and X. Zhan, *Nat. Rev. Mater.*, 2018, **3**, 18003.
5. C. Lee, S. Lee, G.-U. Kim, W. Lee and B. J. Kim, *Chem. Rev.*, 2019, **119**, 8028-8086.
6. G. Wang, F. S. Melkonyan, A. Facchetti and T. J. Marks, *Angew Chem Int Ed Engl*, 2019, **58**, 4129-4142.
7. G. Zhang, F. R. Lin, F. Qi, T. Heumüller, A. Distler, H.-J. Egelhaaf, N. Li, P. C. Y. Chow, C. J. Brabec, A. K. Y. Jen and H.-L. Yip, *Chem. Rev.*, 2022, **122**, 14180-14274.

8. D. Luo, W. Jang, D. D. Babu, M. S. Kim, D. H. Wang and A. K. K. Kyaw, *J. Mater. Chem. A*, 2022, **10**, 3255-3295.
9. H.-W. Cheng, Y. Zhao and Y. Yang, *Adv. Eng. Mater.*, 2022, **12**, 2102908.
10. Q. Liu, Y. Jiang, K. Jin, J. Qin, J. Xu, W. Li, J. Xiong, J. Liu, Z. Xiao, K. Sun, S. Yang, X. Zhang and L. Ding, *Science Bulletin*, 2020, **65**, 272-275.
11. A. S. Gertsen, M. F. Castro, R. R. Søndergaard and J. W. Andreasen, *Flexible and Printed Electronics*, 2020, **5**, 014004.
12. T. Yan, W. Song, J. Huang, R. Peng, L. Huang and Z. Ge, *Adv. Mater.*, 2019, **31**, 1902210.
13. S. Li, C.-Z. Li, M. Shi and H. Chen, *ACS Eng. Lett.*, 2020, **5**, 1554-1567.
14. L. Liu, Y. Kan, K. Gao, J. Wang, M. Zhao, H. Chen, C. Zhao, T. Jiu, A.-K.-Y. Jen and Y. Li, *Adv. Mater.*, 2020, **32**, 1907604.
15. C. Li, J. Zhou, J. Song, J. Xu, H. Zhang, X. Zhang, J. Guo, L. Zhu, D. Wei, G. Han, J. Min, Y. Zhang, Z. Xie, Y. Yi, H. Yan, F. Gao, F. Liu and Y. Sun, *Nature Energy*, 2021, **6**, 605-613.
16. H. Sun, T. Liu, J. Yu, T.-K. Lau, G. Zhang, Y. Zhang, M. Su, Y. Tang, R. Ma, B. Liu, J. Liang, K. Feng, X. Lu, X. Guo, F. Gao and H. Yan, *Eng. Environ. Sci.*, 2019, **12**, 3328-3337.
17. D. Li, N. Deng, Y. Fu, C. Guo, B. Zhou, L. Wang, J. Zhou, D. Liu, W. Li, K. Wang, Y. Sun and T. Wang, *Adv. Mater.*, 2023, **35**, 2208211.
18. K. Liu, Y. Jiang, F. Liu, G. Ran, F. Huang, W. Wang, W. Zhang, C. Zhang, J. Hou and X. Zhu, *Adv. Mater.*, 2023, **35**, 2300363.
19. W. Gao, F. Qi, Z. Peng, F. R. Lin, K. Jiang, C. Zhong, W. Kaminsky, Z. Guan, C.-S. Lee, T. J. Marks, H. Ade and A. K.-Y. Jen, *Adv. Mater.*, 2022, **34**, 2202089.
20. Y. Lin, J. Wang, Z.-G. Zhang, H. Bai, Y. Li, D. Zhu and X. Zhan, *Adv. Mater.*, 2015, **27**, 1170-1174.
21. T. J. Aldrich, M. Matta, W. Zhu, S. M. Swick, C. L. Stern, G. C. Schatz, A. Facchetti, F. S. Melkonyan and T. J. Marks, *Journal of the American Chemical Society*, 2019, **141**, 3274-3287.
22. W. Zhao, S. Li, H. Yao, S. Zhang, Y. Zhang, B. Yang and J. Hou, *Journal of the American Chemical Society*, 2017, **139**, 7148-7151.
23. J. Yuan, Y. Zhang, L. Zhou, C. Zhang, T.-K. Lau, G. Zhang, X. Lu, H.-L. Yip, S. K. So, S. Beaupré, M. Mainville, P. A. Johnson, M. Leclerc, H. Chen, H. Peng, Y. Li and Y. Zou, *Adv. Mater.*, 2019, **31**, 1807577.
24. G. Li, X. Zhang, L. O. Jones, J. M. Alzola, S. Mukherjee, L.-w. Feng, W. Zhu, C. L. Stern, W. Huang, J. Yu, V. K. Sangwan, D. M. DeLongchamp, K. L. Kohlstedt, M. R. Wasielewski, M. C. Hersam, G. C. Schatz, A. Facchetti and T. J. Marks, *Journal of the American Chemical Society*, 2021, **143**, 6123-6139.
25. J. Yuan, Y. Zhang, L. Zhou, G. Zhang, H.-L. Yip, T.-K. Lau, X. Lu, C. Zhu, H. Peng, P. A. Johnson, M. Leclerc, Y. Cao, J. Ulanski, Y. Li and Y. Zou, *Joule*, 2019, **3**, 1140-1151.
26. F. Liu, Z. Zhou, C. Zhang, T. Vergote, H. Fan, F. Liu and X. Zhu, *Journal of the American Chemical Society*, 2016, **138**, 15523-15526.
27. G. Li, L.-W. Feng, S. Mukherjee, L. O. Jones, R. M. Jacobberger, W. Huang, R. M. Young, R. M. Pankow, W. Zhu, N. Lu, K. L. Kohlstedt, V. K. Sangwan, M. R. Wasielewski, M. C. Hersam, G. C. Schatz, D. M. DeLongchamp, A. Facchetti and T. J. Marks, *Eng. Environ. Sci.*, 2022, **15**, 645-659.
28. X. Zhang, G. Li, S. Mukherjee, W. Huang, D. Zheng, L.-W. Feng, Y. Chen, J. Wu, V. K. Sangwan, M. C. Hersam, D. M. DeLongchamp, J. Yu, A. Facchetti and T. J. Marks, *Adv. Eng. Mater.*, 2022, **12**, 2102172.
29. W. Zhu, A. P. Spencer, S. Mukherjee, J. M. Alzola, V. K. Sangwan, S. H. Amsterdam, S. M. Swick, L. O. Jones, M. C. Heiber, A. A. Herzing, G. Li, C. L. Stern, D. M. DeLongchamp, K. L. Kohlstedt, M. C. Hersam, G. C. Schatz, M. R. Wasielewski, L. X. Chen, A. Facchetti and T. J. Marks, *Journal of the American Chemical Society*, 2020, **142**, 14532-14547.
30. G. Li, F. Qin, R. M. Jacobberger, S. Mukherjee, L. O. Jones, R. M. Young, R. M. Pankow, B. P. Kerwin, L. Q. Flag, D. Zheng, L.-W. Feng, K. L. Kohlstedt, V. K. Sangwan, M. C. Hersam, G. C. Schatz, D. M. DeLongchamp, M. R. Wasielewski, Y. Zhou, A. Facchetti and T. J. Marks, *Joule*, 2023, DOI: 10.1016/j.joule.2023.07.005.
31. S. M. Swick, J. M. Alzola, V. K. Sangwan, S. H. Amsterdam, W. Zhu, L. O. Jones, N. Powers-Riggs, A. Facchetti, K. L. Kohlstedt, G. C. Schatz, M. C. Hersam, M. R. Wasielewski and T. J. Marks, *Adv. Eng. Mater.*, 2020, **10**, 2000635.
32. Y. Li, T. Li and Y. Lin, *Materials Chemistry Frontiers*, 2021, **5**, 2907-2930.
33. Y. Wang, J. Lee, X. Hou, C. Labanti, J. Yan, E. Mazzolini, A. Parhar, J. Nelson, J.-S. Kim and Z. Li, *Adv. Eng. Mater.*, 2021, **11**, 2003002.
34. Y. Li, X. Huang, K. Ding, H. K. M. Sheriff, L. Ye, H. Liu, C.-Z. Li, H. Ade and S. R. Forrest, *Nat. Commun.*, 2021, **12**, 5419.
35. L. Hu, Y. Jiang, L. Sun, C. Xie, F. Qin, W. Wang and Y. Zhou, *J. Phys. Chem. Lett.*, 2021, **12**, 2607-2614.
36. S. Park and H. J. Son, *J. Mater. Chem. A*, 2019, **7**, 25830-25837.
37. Y. Zhao, Z. Wu, X. Liu, Z. Zhong, R. Zhu and J. Yu, *J. Mater. Chem. C*, 2021, **9**, 13972-13980.
38. M. A. Anderson, B. W. Larson and E. L. Ratcliff, *ACS Appl. Mater. Inter.*, 2021, **13**, 44641-44655.
39. A. J. Clarke, J. Luke, R. Meitzner, J. Wu, Y. Wang, H. K. H. Lee, E. M. Speller, H. Bristow, H. Cha, M. J. Newman, K. Hooper, A. Evans, F. Gao, H. Hoppe, I. McCulloch, U. S. Schubert, T. M. Watson, J. R. Durrant, W. C. Tsoi, J.-S. Kim and Z. Li, *Cell Reports Physical Science*, 2021, **2**, 100498.
40. A. Azeez and K. S. Narayan, *J. Phys. Chem. C*, 2021, **125**, 12531-12540.
41. Y. Han, H. Dong, W. Pan, B. Liu, X. Chen, R. Huang, Z. Li, F. Li, Q. Luo, J. Zhang, Z. Wei and C.-Q. Ma, *ACS Appl. Mater. Inter.*, 2021, **13**, 17869-17881.
42. X. Zhu, L. Hu, W. Wang, X. Jiang, L. Hu and Y. Zhou, *ACS Applied Energy Materials*, 2019, **2**, 7602-7608.
43. K. An, W. Zhong, F. Peng, W. Deng, Y. Shang, H. Quan, H. Qiu, C. Wang, F. Liu, H. Wu, N. Li, F. Huang and L. Ying, *Nat. Commun.*, 2023, **14**, 2688.
44. N. Y. Doumon, M. V. Dryzhov, F. V. Houard, V. M. Le Corre, A. Rahimi Chatri, P. Christodoulis and L. J. A. Koster, *ACS Appl. Mater. Inter.*, 2019, **11**, 8310-8318.
45. E. M. Speller, A. J. Clarke, N. Aristidou, M. F. Wyatt, L. Francàs, G. Fish, H. Cha, H. K. H. Lee, J. Luke, A. Wadsworth, A. D. Evans, I. McCulloch, J.-S. Kim, S. A. Haque, J. R. Durrant, S. D. Dimitrov, W. C. Tsoi and Z. Li, *ACS Eng. Lett.*, 2019, **4**, 846-852.
46. J. Guo, Y. Wu, R. Sun, W. Wang, J. Guo, Q. Wu, X. Tang, C. Sun, Z. Luo, K. Chang, Z. Zhang, J. Yuan, T. Li, W. Tang, E. Zhou, Z. Xiao, L. Ding, Y. Zou, X. Zhan, C. Yang, Z. Li, C. J.

- Brabec, Y. Li and J. Min, *J. Mater. Chem. A*, 2019, **7**, 25088-25101.
47. W. Li, D. Liu and T. Wang, *Adv. Funct. Mater.*, 2021, **31**, 2104552.
 48. T. Liu, Q. C. Burlingame, M. R. Ivancevic, X. Liu, J. Hu, B. P. Rand and Y.-L. Loo, *Adv. Eng. Mater.*, 2023, **13**, 2300046.
 49. Z.-X. Liu, Z.-P. Yu, Z. Shen, C. He, T.-K. Lau, Z. Chen, H. Zhu, X. Lu, Z. Xie, H. Chen and C.-Z. Li, *Nat. Commun.*, 2021, **12**, 3049.
 50. U. Rau and H. W. Schock, *Appl. Phys. A*, 1999, **69**, 131-147.
 51. D. Bozyigit, W. M. M. Lin, N. Yazdani, O. Yarema and V. Wood, *Nat. Commun.*, 2015, **6**, 6180.
 52. S. S. Hegedus and W. N. Shafarman, *Progress in Photovoltaics: Research and Applications*, 2004, **12**, 155-176.
 53. K. Tvingstedt and C. Deibel, *Adv. Eng. Mater.*, 2016, **6**, 1502230.
 54. P. Singh and N. M. Ravindra, *Sol. Energy Mater. Sol. Cells*, 2012, **101**, 36-45.
 55. W. Dawidowski, B. Ściana, K. Bielak, M. Mikolášek, J. Drobný, J. Serafińczuk, I. Lombardero, D. Radziejewicz, W. Kijaszek, A. Kósa, M. Florovič, J. Kováč, C. Algora and L. u. Stuchlíková, *Energies*, 2021, **14**, 4651.
 56. M. P. Hughes, K. D. Rosenthal, N. A. Ran, M. Seifrid, G. C. Bazan and T.-Q. Nguyen, *Adv. Funct. Mater.*, 2018, **28**, 1801542.
 57. X. Zhang, C. Li, J. Xu, R. Wang, J. Song, H. Zhang, Y. Li, Y.-N. Jing, S. Li, G. Wu, J. Zhou, X. Li, Y. Zhang, X. Li, J. Zhang, C. Zhang, H. Zhou, Y. Sun and Y. Zhang, *Joule*, 2022, **6**, 444-457.
 58. G. Zhang, X.-K. Chen, J. Xiao, P. C. Y. Chow, M. Ren, G. Kuppang, X. Jiao, C. C. S. Chan, X. Du, R. Xia, Z. Chen, J. Yuan, Y. Zhang, S. Zhang, Y. Liu, Y. Zou, H. Yan, K. S. Wong, V. Coropceanu, N. Li, C. J. Brabec, J.-L. Bredas, H.-L. Yip and Y. Cao, *Nat. Commun.*, 2020, **11**, 3943.
 59. R. A. Awani, Z. Song, C. Chen, C. Li, C. Wang, M. A. Razooqi, L. Chen, X. Wang, R. J. Ellingson, J. V. Li and Y. Yan, *Joule*, 2020, **4**, 644-657.
 60. D. Bozyigit, S. Volk, O. Yarema and V. Wood, *Nano Lett.*, 2013, **13**, 5284-5288.
 61. T. Walter, R. Herberholz, C. Müller and H. W. Schock, *J. Appl. Phys.*, 1996, **80**, 4411-4420.
 62. S. Wang, P. Kaenburgh, B. Klingebiel, D. Schillings and T. Kirchartz, *J. Phys. Chem. C*, 2018, **122**, 9795-9803.
 63. J. A. Carr, M. Elshobaki and S. Chaudhary, *Appl. Phys. Lett.*, 2015, **107**, 203302.
 64. G. Yang, R. A. C. M. M. v. Swaaij, S. Dobrovolskiy and M. Zeman, *J. Appl. Phys.*, 2014, **115**, 034512.
 65. H.-S. Duan, H. Zhou, Q. Chen, P. Sun, S. Luo, T.-B. Song, B. Bob and Y. Yang, *Phys. Chem. Chem. Phys.*, 2015, **17**, 112-116.
 66. V. K. Sangwan, M. Zhu, S. Clark, K. A. Luck, T. J. Marks, M. G. Kanatzidis and M. C. Hersam, *ACS Appl. Mater. Inter.*, 2019, **11**, 14166-14174.
 67. D. Kroh, S. Athanasopoulos, V. Nádaždy, F.-J. Kahle, H. Bässler and A. Köhler, *Adv. Funct. Mater.*, 2023, 2302520.
 68. J. Nelson, *The Physics of Solar Cells*, Imperial College Press, 2003.
 69. S. R. Cowan, A. Roy and A. J. Heeger, *Phys. Rev. B*, 2010, **82**, 245207.
 70. L.-W. Feng, J. Chen, S. Mukherjee, V. K. Sangwan, W. Huang, Y. Chen, D. Zheng, J. W. Strzalka, G. Wang, M. C. Hersam, D. DeLongchamp, A. Facchetti and T. J. Marks, *ACS Eng. Lett.*, 2020, **5**, 1780-1787.
 71. N. D. Eastham, J. L. Logsdon, E. F. Manley, T. J. Aldrich, M. J. Leonardi, G. Wang, N. E. Powers-Riggs, R. M. Young, L. X. Chen, M. R. Wasielewski, F. S. Melkonyan, R. P. H. Chang and T. J. Marks, *Adv. Mater.*, 2018, **30**, 1704263.
 72. A. J. Gillett, A. Privitera, R. Dilmurat, A. Karki, D. Qian, A. Pershin, G. Londi, W. K. Myers, J. Lee, J. Yuan, S.-J. Ko, M. K. Riede, F. Gao, G. C. Bazan, A. Rao, T.-Q. Nguyen, D. Beljonne and R. H. Friend, *Nature*, 2021, **597**, 666-671.
 73. G. Lo Gerfo M, L. Bolzonello, F. Bernal-Tezca, J. Martorell and N. F. van Hulst, *J. Phys. Chem. Lett.*, 2023, **14**, 1999-2005.
 74. A. J. Carrod, V. Gray and K. Börjesson, *Eng. Environ. Sci.*, 2022, **15**, 4982-5016.
 75. P. Jiang, L. Hu, L. Sun, Z. a. Li, H. Han and Y. Zhou, *Chem. Sci.*, 2022, **13**, 4714-4739.
 76. F. C. Löhner, C. Senfter, C. J. Schaffer, J. Schlipf, D. Moseguí González, P. Zhang, S. V. Roth and P. Müller-Buschbaum, *Adv. Phot. Res.*, 2020, **1**, 2000047.
 77. M. Jørgensen, K. Norrman, S. A. Gevorgyan, T. Tromholt, B. Andreasen and F. C. Krebs, *Adv. Mater.*, 2012, **24**, 580-612.
 78. W. R. Mateker, T. Heumueller, R. Cheacharoen, I. T. Sachs-Quintana, M. D. McGehee, J. Warnan, P. M. Beaujuge, X. Liu and G. C. Bazan, *Chem. Mater.*, 2015, **27**, 6345-6353.
 79. L. Zhu, M. Zhang, G. Q. Zhou, T. Y. Hao, J. Q. Xu, J. Wang, C. Q. Qiu, N. Prine, J. Ali, W. Feng, X. D. Gu, Z. F. Ma, Z. Tang, H. M. Zhu, L. Ying, Y. M. Zhang and F. Liu, *Adv. Eng. Mater.*, 2020, **n/a**, 1904234.
 80. H. Xu, J. Han, S. Chen, Y. Liu, L. Huerta Hernandez, J. Bertrandie, M. Babics, S. Alam, D. R. Villalva, S. H. K. Paleti, J. Gorenflot, C. Herok, N. Ramos, J. Troughton, A. Sharma, T. B. Marder, B. Engels, J. Martin, S. De Wolf, F. Laquai and D. Baran, *Joule*, 2023, DOI: 10.1016/j.joule.2023.07.003.
 81. B. Movaghar, L. O. Jones, M. A. Ratner, G. C. Schatz and K. L. Kohlstedt, *J. Phys. Chem. C*, 2019, **123**, 29499-29512.
 82. B. Zhou, L. Wang, Y. Liu, C. Guo, D. Li, J. Cai, Y. Fu, C. Chen, D. Liu, Y. Zhou, W. Li and T. Wang, *Adv. Funct. Mater.*, 2022, **32**, 2206042.
 83. N. Zhou, M.-G. Kim, S. Loser, J. Smith, H. Yoshida, X. Guo, C. Song, H. Jin, Z. Chen, S. M. Yoon, A. J. Freeman, R. P. H. Chang, A. Facchetti and T. J. Marks, *Proc. Natl. Acad. Sci. U.S.A.*, 2015, **112**, 7897-7902.
 84. E. Trippodo, V. Campisciano, L.-W. Feng, Y. Chen, W. Huang, J. M. Alzola, D. Zheng, V. K. Sangwan, M. C. Hersam, M. R. Wasielewski, B. Pignataro, F. Giacalone, T. J. Marks and A. Facchetti, *J. Mater. Chem. C*, 2023, **11**, 8074-8083.
 85. N. Tanaka, M. Nakano, T. Kobayashi, A. Takahara, T. Fujinuki, M. Shahiduzzaman, M. Karakawa, T. Taima and K. Iiyama, *Macromol. Rapid Comm.*, 2022, **43**, 2100718.
 86. Y. Wang, J. Luke, A. Privitera, N. Rolland, C. Labanti, G. Londi, V. Lemaure, D. T. W. Toolan, A. J. Sneyd, S. Jeong, D. Qian, Y. Olivier, L. Sorace, J.-S. Kim, D. Beljonne, Z. Li and A. J. Gillett, *Joule*, 2023, **7**, 810-829.