

A General Synthesis of Cyclic Bottlebrush Polymers With Enhanced Mechanical Properties via Graft-Through Ring Expansion Metathesis Polymerization

Matthew J. Elardo,^a Adelaide M. Levenson,^a Ana Paula Kitos Vasconcelos,^a Meredith N. Pomfret,^a and Matthew R. Golder^{*a}

^aDepartment of Chemistry and Molecular Engineering & Science Institute
University of Washington
36 Bagley Hall, Seattle, WA 98195
E-mail: goldermr@uw.edu

Abstract: Bottlebrush polymers represent an important class of macromolecular architectures, with applications ranging from drug delivery to organic electronics. While there is an abundance of literature describing the synthesis, structure, and applications of linear bottlebrush polymers using ring-opening metathesis polymerization (ROMP), there are comparatively less reports on their cyclic counterparts. This lack of research is primarily due to the difficulty in synthesizing cyclic bottlebrush polymers, as extensions of typical routes towards linear bottlebrush polymers (i.e., “grafting-through” polymerizations of macromonomers with ROMP) produce only ultrahigh molar mass cyclic bottlebrush polymers with poor molar mass control. Herein, we report a ring-expansion metathesis polymerization (REMP) approach to cyclic bottlebrush polymers via a “grafting-through” approach utilizing the active **pyr-CB6** initiator developed in our lab. The resulting polymers, characterized via GPC-MALS-IV, are shown to have superior molar mass control across a range of target backbone lengths. The cyclic materials are also found to have superior mechanical properties when compared to their linear counterparts, as assessed by ball-mill grinding and compression testing experiments.

Introduction

The manipulation of polymer topology is a major area of interest in synthetic macromolecular chemistry due to the impact of architecture on material properties. Recent advances in this area have led to the development of a wide variety of intricate synthetic polymer architectures with defined chain ends, such as star polymers¹, dendrimers², and bottlebrush polymers^{3–6}. Of particular interest, however, are variants *without* chain ends, namely cyclic polymers, as this specific topology has markedly different properties when compared to linear counterparts, such as higher glass transition temperatures, higher decomposition temperatures, and lower intrinsic viscosities^{7–9}. Acyclic bottlebrush polymers^{3,6} are linear polymers with densely grafted macromolecular sidechains; the chemical makeup of the backbone and sidechains intimately control rich solution-state and bulk phenomena including self-assembly^{10–12} and stimuli-responsiveness in thin films¹³. As such, these polymer bottlebrush architectures have found diverse applications from drug delivery^{14–17} to organic photonics^{18–22}. There has therefore been intense interest in the development of new linear bottlebrush materials using well-established synthetic paradigms. These strategies can be broken into three general categories: “grafting-to”²³, “grafting-from”²⁴, and “grafting-through”²⁵. Of these three distinct synthetic classes, the “grafting-through” method is most desirable because of precise control over features such as grafting density (where high densities up to 100% are easily achievable), brush length, and brush dispersity, but is synthetically challenging due to the steric demands of the polymerizable “macromonomer”²⁶. For ROMP-derived materials, this problem has been largely solved by the development of advanced olefin metathesis initiators^{27,28}, which produce bottlebrush polymers with narrow dispersities and good control over molar mass, even when

using large and/or branched macromonomers^{12,25,29}.

While examples of linear bottlebrush polymers (BBPs) abound in the literature^{6,12–16,18}, instances of their cyclic analogues are comparatively sparse. This difference is due to the various challenges associated with cyclic polymer synthesis. One major synthetic approach towards cyclic BBPs, linear ring closure, involves synthesizing a telechelic linear pre-polymer; functional end groups react with each other to form the desired macrocycle. However, this approach inevitably results in linear contaminants from acyclic couplings, requires dilute reaction conditions, and is not suitable for the generation of high molar mass materials^{30,31}. Nevertheless, this approach allowed access to multiblock cyclic polymers and provided early evidence for unique self-assembly profiles³¹. The second major synthetic approach is ring expansion polymerization, of which ring expansion metathesis polymerization (REMP, the cyclic analogue to ROMP) is a common variant^{32,33}. Early examples of REMP initiators suffer from poor molar mass control and polydisperse products, especially when performing “graft-through” reactions with large macromonomers³⁴. For instance, Grubbs used this approach to prepare cyclic bottlebrush polymers with macrocyclic alkylidene REMP initiators (e.g., **SC-5**); however, only ultra-high molar mass materials were reported³⁴. Due to the inherent difficulty in controlled cyclic bottlebrush polymer growth using “grafting-through”, cyclic BBPs are often prepared via “grafting-from” (**Figure 1A**)^{35–40}.

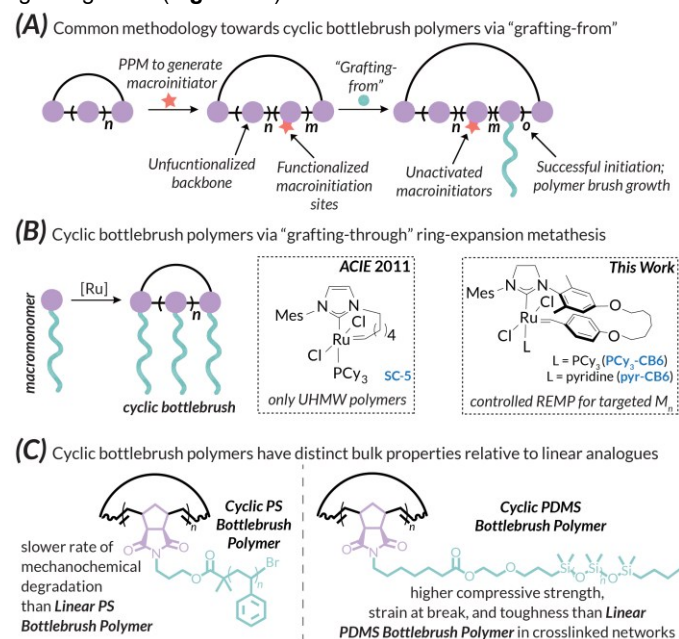



Figure 1: (A) General paradigm for cyclic bottlebrush polymer synthesis via “grafting-from”; (B) Approaches towards cyclic bottlebrush polymers using Ru-mediated REMP. (C) Summary of bulk property enhancements for cyclic **PS-BBP** and cyclic **PDMS-BBP** with respect to comparable linear analogues.

Despite their challenging syntheses, cyclic bottlebrush polymers hold promise in enhanced capacity for drug delivery^{41,42} and self-assembly into a variety of nanostructures, (e.g., supramolecular tubes, rods, plates, spheres, and worm architectures^{31,43,44}). Hence, there is great potential for the development of functional materials using cyclic bottlebrush polymers made with a “grafting-from” approach (**Figure 1B**). In this work, we report a controlled synthetic route toward cyclic bottlebrush polymers utilizing the novel REMP initiator **pyr-CB6** developed within our research group (**Figure 1B**)^{32,45}. We demonstrate excellent control over molar mass with narrow dispersity utilizing macromonomers with disparate thermomechanical properties – “hard” **PS-MM** (i.e., high T_g , rigid, brittle; PS = polystyrene, **Figures S22 – S25**) and “soft” **PDMS-MM** (i.e., low T_g , flexible, elastomeric; PDMS = polydimethylsiloxane, **Figures S19 & S20**) macromonomers. The resultant polymers are characterized, and their cyclic topologies confirmed, via gel permeation chromatography coupled with multi-angle light scattering, intrinsic viscometry, and refractive index detectors (GPC-MALS-IV-RI; see **Figures S26 – S33** for representative DRI traces and **Figures S45 – S50** for representative viscosity plots). The thermal, mechanochemical, and mechanical properties of the bulk materials and crosslinked networks thereof were probed via a combination of differential scanning calorimetry (DSC), thermogravimetric analysis (TGA), ball-mill grinding mechanochemistry (BMG), and compression testing (**Figure 1C**). Overall, the efforts described herein encompass a straightforward approach towards cyclic bottlebrush polymers and currently represent the most well-controlled “grafting-through” methodology to access them to date. In other words, this methodology allows for the preparation of cyclic bottlebrush polymers with the same ease as their acyclic counterparts.

Synthesis and Solution-State Analysis

We began our investigations by probing the activity of less active **PCy₃-CB6** for **PS-MM** and **PDMS-MM** REMP reactions. Interestingly, even when targeting a relatively short backbone degree of polymerization (backbone DP = 25), **PDMS-MM** afforded material with much higher-than-expected M_n (by nearly two orders of magnitude) and a broad GPC-RI trace with a sizeable low molar mass shoulder; **PS-MM** afforded material that was too viscous for subsequent analysis (**Table 1** and **Figure S40**). Despite **PCy₃-CB6** providing superior molar mass control relative to those of cyclic alkylidene initiators (e.g., **UC-5**, **UC-6**) in our prior REMP studies with norbornene monomers³², the steric hinderance of macromonomers provide additional kinetic challenges. Fortunately, initial REMP experiments employing the more active **pyr-CB6** initiator indicated rapid and complete macromonomer consumption (< 1 h) in DCE at 55 °C (**Figures S36 & S37**). Notably, we do not observe any molar mass evolution at extended reaction times following macromonomer conversion (**Figures S36 & S37**), a feature we reported previously which distinguishes **pyr-CB6** mechanistically from **PCy₃-CB6**⁴⁵. Furthermore, we observe a significant improvement in molar mass control, dispersity, and peak structure when utilizing **pyr-CB6** in place of **PCy₃-CB6** for “grafting-through” REMP towards well-defined cyclic bottlebrush macromolecules. We believe that an increased initiator efficiency combined with relatively slow secondary metathesis (i.e., intermolecular chain transfer) leads to the large disparity in initiator-dependent experimental M_n (**Table 1**).

Table 1: GPC characterization of **PDMS-MM**^[a] REMP initiated by **CB6** (with and without pyridine)

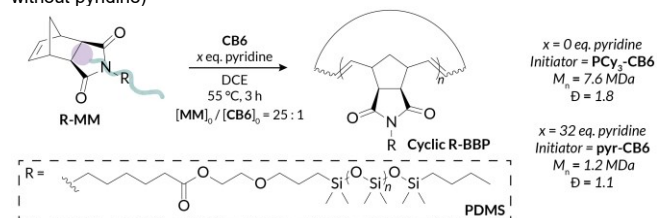

Pyridine Eq.:	Theoretical DP ^[b]	Experimental DP ^[c]	Theoretical <i>M_n</i> (kDa) ^[b]	Experimental <i>M_n</i> (kDa) ^[c]	<i>Đ</i> ^[c]
0	25	1086	180	7600	1.8
32	25	171	180	1200	1.1


^[a] **PDMS-MM** $M_n = 7.0$ kDa

^[b] Calculated by $[\text{MM}]_0/[\text{I}]_0$, where $[\text{MM}]$ is the molar amount of PDMS-MM and $[\text{I}]$ is the molar amount of CB6.

^[c] Determined by GPC-MALS

We next investigated the ability of our **pyr-CB6** initiator to prepare cyclic bottlebrush polymers at a variety of target molar masses (i.e., a range of target backbone DP). A major challenge encountered with cyclic Ru alkylidene initiators utilized by Grubbs is their inability to prepare low DP polymers due to poor initiation efficiency; this shortcoming is especially true when targeting bottlebrush polymers via “grafting-through” of macromonomers.³⁴ We observe good molar mass control over a wide range of target DPs (DP = 10 – 50) (**Table 2**) while maintaining low dispersities for both **PS-MM (Figure 2A)** and **PDMS-MM. (Figure 2B)**. The result of the improved initiation efficiency is cyclic bottlebrush polymers with M_n <50 kDa, a significant improvement from previous systems which were limited to ultra-high molar mass polymers in the MDa regime. Hence, our methodology showcases the most powerful examples to date of controlling cyclic bottlebrush backbone DP with “grafting-through” technology.

Table 2: GPC characterization of cyclic REMP BBPs at varying backbone target degrees of polymerization (DP)

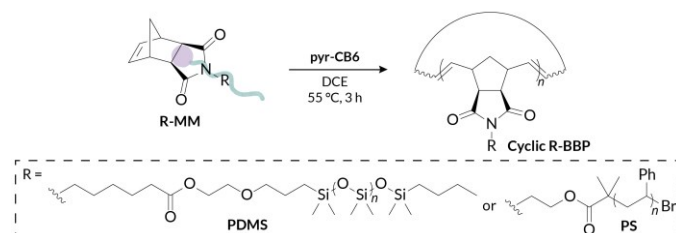

Monomer ^[a]	Theoretical DP ^[b]	Measured DP ^[c]	Theoretical M_n (kDa) ^[b]	Measured M_n (kDa) ^[c]	$\bar{D}^{[c]}$
PS-MM	10	18	46	83	1.1
PS-MM	20	28	90	130	1.1
PS-MM	30	37	140	170	1.2
PS-MM	40	43	180	200	1.2
PS-MM	50	52	230	240	1.3
PDMS-MM	10	41	63	260	1.1
PDMS-MM	20	81	130	510	1.1
PDMS-MM	30	114	190	720	1.1
PDMS-MM	40	151	250	950	1.2
PDMS-MM	50	175	320	1100	1.2

^[a] **PS-MM** $M_n = 4.6$ kDa; **PDMS-MM** $M_n = 6.3$ kDa

^[b] Calculated by $[\text{MM}]_0/[\text{I}]_0$, where $[\text{MM}]$ is the molar amount of macromonomer and $[\text{I}]$ is the molar amount of **CB6** (plus 32 eq. pyridine)

^[c] Determined by GPC-MALS

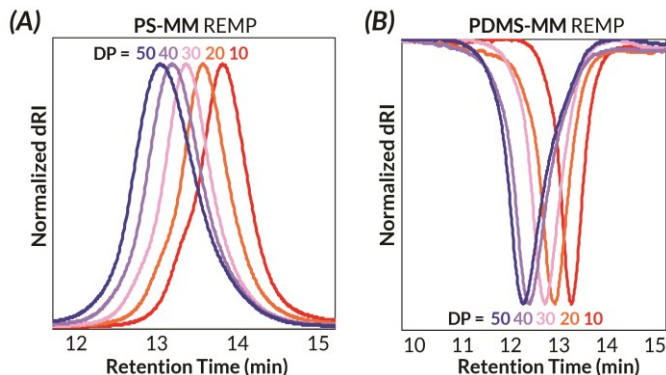


Figure 2: Solution-state characterization of (A) **PS-MM** and (B) **PDMS-MM** REMP by GPC-MALS-RI for target DP = 10 – 50.

Another challenge with preparing cyclic bottlebrush polymers via “grafting-through” REMP is that the polymerizations do not work well even with modest sized macromonomers. For instance, in the seminal report of this methodology from Grubbs using **SC-5** and **SC-6**, they observe only 65% conversion of **PS-MM** ($M_n = 6.6$ kDa)³⁴. Here, we demonstrate that analogous REMP utilizing **pyr-CB6** works well for even larger macromonomers; increasing the brush length (**PS-MM**, $M_n = 8.3$ kDa) does not have a detrimental impact on molar mass control and only modestly increases the dispersity of the resulting cyclic bottlebrush polymer (**Figure S38** and **Table S3**). Although more dilute conditions are required to maintain molar mass control (ca. 40 mg/mL, versus ca. 90 mg/mL for the lower molar mass **PS-MM**), the reaction is nearly quantitative with >90% monomer conversion after 3.5 hours as assessed by GPC-RI (**Figure S39**).

We next probed the topology of the putative cyclic bottlebrush polymers in dilute solution via GPC with in-line multi-angle light scattering, viscometry, and refractive index detectors (GPC-MALS-IV-RI). To determine absolute molar masses, we directly measured the specific refractive index increment (i.e., dn/dc) for representative ROMP and REMP bottlebrush polymers (**Figures S51 – S58** and **Table S4**). Interestingly, cyclic bottlebrush polymers derived from both **PS-MM** and **PDMS-MM** had lower magnitude dn/dc values relative to linear analogs in CHCl_3 ; topology dependent refractive indices have been observed in other organic polymer scaffolds as well^{46–48}. In general, we observe longer retention times in the GPC analysis of REMP bottlebrush polymers when compared to ROMP bottlebrush polymers of similar molar masses prepared using Grubbs 3 initiator (see SI for experimental details) for both **PS-MM** (**Figure 3A**) and **PDMS-MM** (**Figure 3B**) REMP reactions. Likewise, plots of molar mass vs. GPC retention time indicate higher molar masses for the REMP polymers across all elution volumes (**Figures S43 & S44**). These results collectively indicate that the REMP polymers are more compact in solution than their ROMP counterparts of similar molar mass, a feature that is characteristic of cyclic polymers due to their lack of chain ends^{7–9}.

Similarly, Mark-Houwink-Sakurada (MHS) analyses of the REMP BBPs reveal significantly lower intrinsic viscosities than for ROMP BBPs of similar molar mass ($[\eta]_{\text{cyclic}}/[\eta]_{\text{linear}} = \text{ca. } 0.57 - 0.63$) for both **PS** (**Figure 4A**) and **PDMS** (**Figure 4B**)^{7–9}. As the bottlebrush polymers presented in this study have comparatively short backbone DPs relative to prior “grafting-through” REMP studies³⁴, dilute solution-state behavior as assessed by intrinsic viscosity measurements suggests deviation from Flory-Fox behavior (i.e., $[\eta] \sim M^{0.7}$).⁴⁹ Specifically, only a small increase in intrinsic viscosity with increasing molar mass is observed with a Mark-Houwink parameter, α , between ca. 0.3 – 0.4 (**Figures S45 – S50**). These data suggest that the bottlebrush polymers in this study, all with relatively short backbone DPs, behave more like star-polymers in solution⁴⁹. Nonetheless, importantly both ROMP and

REMP polymers have similar Mark-Houwink parameters and therefore differences in the observed intrinsic viscosities are due to molecular architecture (i.e., linear versus cyclic) rather than differences in backbone structure and/or conformation³³.

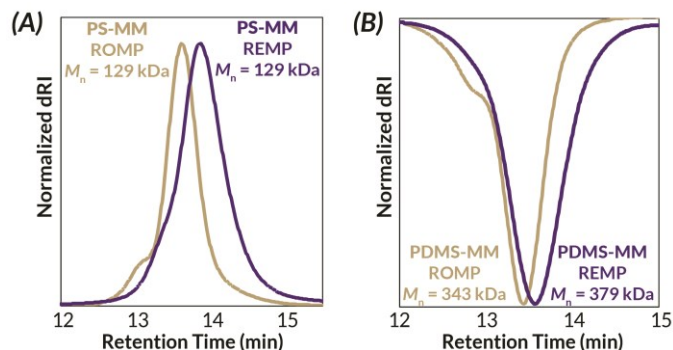


Figure 3: Solution-state characterization of cyclic and linear (A) **PS-BBP** and (B) **PDMS-BBP** by GPC-MALS-RI.

We also used the collective analytical approaches described above to qualitatively probe the efficiency of polymer backbiting by comparing the GPC-RI traces and MHS plots of quenched (i.e., ethyl vinyl ether, EVE, was added at the end of the polymerization reaction) and unquenched aliquots from the same samples (**Figures S34, S35, S47, & S50** and **Tables S1 - S2**). If backbiting is incomplete and Ru remains in the cyclic polymer backbone, quenching with EVE produces linear polymers following macrocycle opening via cross-metathesis. This process would result in a shift to shorter retention times and higher intrinsic viscosities in the GPC-RI traces and MHS plots, respectively. We see no significant difference in either of these parameters between quenched and unquenched aliquots from our reaction mixtures, indicating that backbiting is operative insofar as we can measure.

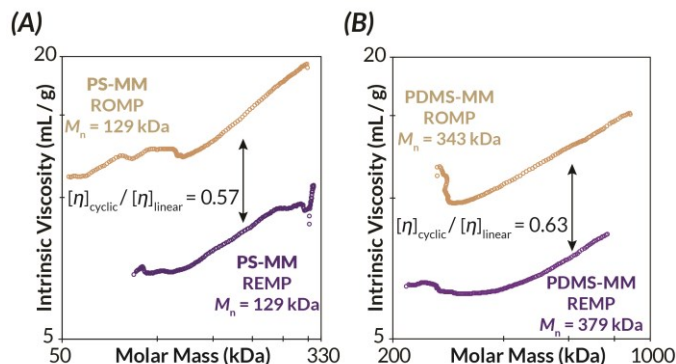


Figure 4: Mark-Houwink-Sakurada plots of cyclic and linear (A) **PS-BBP** and (B) **PDMS-BBP** as measured by GPC-MALS-IV-RI.

Thermal and Mechanical Properties

With two classes of cyclic bottlebrush polymers in hand, we next turned our attention to evaluating the impact of topology on bulk properties of our bottlebrush polymers. We began by probing the thermal properties of linear and cyclic **PS** bottlebrush polymers ($M_n = 129$ kDa), by thermal gravimetric analysis (TGA) and differential scanning calorimetry. Interestingly, we found no significant differences in the thermal stability via TGA ($T_d = 374$ °C and 368 °C for linear and cyclic **PS-BBPs**, respectively) or thermal transition temperature via DSC ($T_g = 100$ °C and 95 °C for linear and cyclic **PS-BBPs**, respectively) between the linear and cyclic samples (**Figures S59 – S62**). While cyclic polymers are known to exhibit higher decomposition temperatures (T_d) and glass transition (T_g) temperatures, we surmise that the high mass percentage of polymeric brush in each sample obfuscates subtle topology-dependent thermal differences. Because of the similar thermal

properties of our **PS** bottlebrush polymers, we next decided to probe the mechanical stability of the bulk **PS** brushes by subjecting them to ball-mill grinding (BMG) conditions. While separate studies have been conducted by Peterson, Kim, Hwang, and Choi probing the relative independent stability of cyclic⁵⁰ and bottlebrush⁵¹ polymers to linear analogues under ball-milling conditions, no work has been done exploring the relative stability of cyclic *bottlebrush* polymers under these conditions. Since it has been previously demonstrated that the degradation rates of linear polymers under BMG conditions scale linearly with increasing T_g ⁵², a feature not observed in either cyclic⁵⁰ or bottlebrush systems⁵¹, and that cyclic polymers tend to degrade slower than linear polymers with of comparable M_n under these conditions⁵⁰, we hypothesized that the cyclic brush polymers may have unique stability to mechanochemical degradation in the solid state. Indeed, we observed that a linear **PS-BBP** ($M_n = 200$ kDa) degraded approximately 30% faster than a cyclic **PS-BBP** ($M_n = 250$ kDa) (**Figure 5** and **S41 & S42**; see **SI Section 8** for experimental details and **Table S5 & S6** for raw data). Thus, we have demonstrated the ability to create materials with enhanced mechanical stability without perturbing thermal properties. This finding, in conjunction with previous findings demonstrating the improved wear resistance and shear stability of cyclic polymer brushes⁵³, may be desirable for applications in polymer coatings such as antifouling materials, where abrasion and impact damage shorten the material's lifespan.⁵⁴

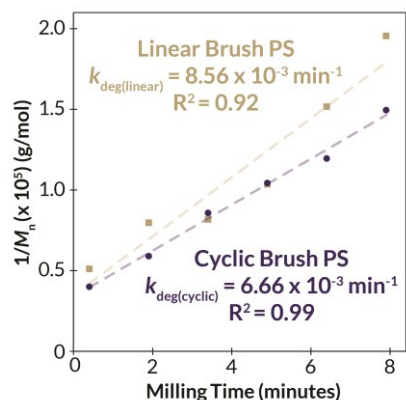


Figure 5: Degradation kinetics for cyclic (purple) and linear (gold) **PS-BBPs** under ball-mill grinding conditions. The inverse of the number-average molar mass was determined for each polymer at each timepoint, and linear regressions were performed to determine the line of best fit (dashed lines). Rate constants were determined by multiplying the slope of each trendline by the number average molar mass of **PS-MM**. See **SI Section 8** for details.

We next turned our attention to the **PDMS-BBP** samples for bulk characterization. These studies were inspired by the universal bottlebrush polymer crosslinking methodology developed by Bates⁵⁵ previously used to prepare supersoft elastomers from **PDMS** bottlebrush polymers⁵⁶. In this work, bifunctional benzophenone **BisBP-PDMS** initiator facilitated indiscriminate brush C-H abstraction and subsequent curing under photochemical irradiation (**Figure 6A**). We reasoned that these mild crosslinking conditions would allow us to explore the impact of bottlebrush polymer topology on the resulting materials' mechanical properties. While we are the first to explore the mechanical properties of crosslinked cyclic *bottlebrush* networks, previous independent work from Tew, Sun, and Veige and Sumerlin have found that cyclic polymer networks have greater compressibility⁵⁷ and stretchability⁵⁸, greater swelling ratios in organic solvent^{57,59}, and increased toughness⁵⁸ when compared to networks prepared from linear analogues. Therefore, we reasoned that such phenomena would extend to our cyclic **PDMS-BBP** networks and hypothesized that they should have superior mechanical properties compared to networks made from linear **PDMS-BBP** at the same crosslinking density. We accordingly synthesized crosslinked networks from high molar mass linear (ROMP, $M_n = 1.65$ MDa) and cyclic (REMP, $M_n = 3.27$ kDa) **PDMS-BBP** samples with a crosslinking density (χ) of 1

mol **BisBP-PDMS** per individual brush in the bottlebrush polymer (i.e., for $\chi = 1.00$, $n_{\text{crosslinker}} = n_{\text{bottlebrush}} * DP_{\text{bottlebrush}}$). It should be noted that while there is a slight mismatch between bottlebrush polymer absolute molar masses, because cyclic polymers are more compact than their linear counterparts, the **PDMS-BBP** precursors to these network samples are actually quite comparable due to similar radii of gyration ($R_g = \text{ca. } 20 - 25$ nm). Furthermore, in their work with cyclic polymer gels, Tew found no change in mechanical properties upon doubling the molar mass of the linear polymer precursor,⁵⁷ and Sumerlin and Veige reported mechanical data for cyclic polymers ca. 1.5 times larger than their linear analogues⁵⁹. We thus reasoned that the slightly higher molar mass of our cyclic BBPs was unlikely to obfuscate any difference in mechanical properties between the samples. Consistent with reports on the aforementioned cyclic polymer networks (*vide supra*), our cyclic **PDMS-BBP** demonstrated significantly ($p < 0.001$) higher swelling ratios (191%) in ethyl acetate than their linear analogues. (148%). Upon compression testing of freshly cured cylindrical specimens (**Figure 6B**), indeed while both networks had similar Young's moduli (762 and 721 kPa, respectively), networks prepared from cyclic **PDMS-BBP** demonstrated statistically significant increases in compressive strength, strain at break, and toughness ($p < 0.01$ for all parameters, $n = 3$) compared to those prepared from linear **PDMS-BBP** at $\chi = 1.00$ (**Figure 6C**; see **Figures S63 – S67** for statistical analysis results and **Table S7** for numerical values).

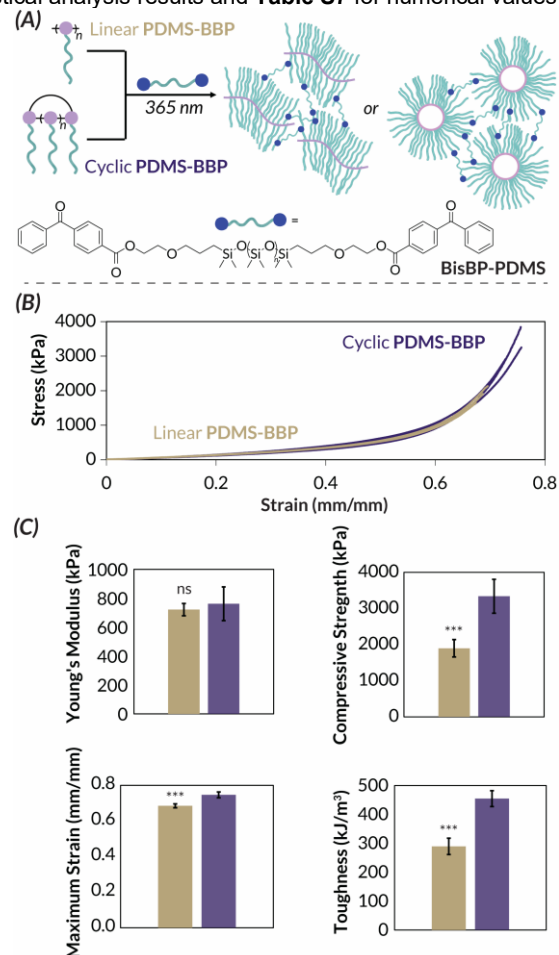


Figure 6: (A): Cartoon demonstrating cross-linking chemistry. (B): Stress-strain curve for linear (gold) and cyclic (purple) **PDMS-BBP** networks in compression tests. (C): Selected mechanical properties of linear (gold) and cyclic (purple) **PDMS-BBP** networks. ***: $p < 0.01$ for $n = 3$. ns: no significance ($p > 0.05$) for $n = 3$.

With such broad utility for **PDMS**-based bottlebrush networks across applications in soft robotics⁶⁰, sensors^{56,61}, and electronics⁶², it is significant that polymer topology alone can enhance mechanical properties. More generally, we anticipate these collective findings to advance the molecular engineering of mechanically robust

bottlebrush polymers networks⁶³ where backbone topology, rather than chemical composition, controls bulk behavior.

Conclusions

In conclusion, we demonstrate in this report an efficient and general methodology for the synthesis of macrocyclic bottlebrush polymers via “grafting-through”. Our approach, which takes advantage of the superior initiation efficiency of our cyclic benzylidene REMP initiator **pyr-CB6**, produces densely grafted macrocyclic bottlebrush polymers with good control over molar mass and dispersity. We report a significant improvement over previous cyclic Ru alkylidene initiators to this end, especially with respect to preparing lower molar mass (<100 kDa) backbones and polymers with long brush lengths (>5 kDa). We demonstrate that the methodology is general, with the ability to tune the parent macromonomer composition and resultant backbone length easily and independently. The cyclic topology of these bottlebrush polymers was interrogated using solution-state analyses (GPC-MALS-IV-R1). Moreover, the bulk thermal and mechanical properties of the BBPs were probed. It was found that despite similar thermal properties, the cyclic **PS-BBP** materials are more stable to mechanochemical degradation than their linear counterparts under ball-mill grinding conditions. Furthermore, we found significant enhancements to the mechanical properties of crosslinked **PDMS-BBP** elastomers with cyclic topologies. Compared to networks prepared from linear **PDMS-BBP**, our elastomers prepared from cyclic **PDMS-BBP** had statistically significant higher compressive strength, strain at break, toughness, and swelling ratio. We envision this methodology finding broad appeal in the development of well-defined macrocyclic bottlebrush polymers for applications spanning porous materials, mechanically resilient coatings/lubricants, tougher soft robotics, and self-assembled nanoarchitectures.

Author Contributions

M.J.E., A.M.L., and M.R.G. conceived of the idea. M.J.E., A.M.L., and M.N.P. conducted synthetic experiments and analyzed physical properties. M.J.E. conducted ball-milling experiments. A.P.K.V. performed mechanical testing experiments. M.J.E. and M.R.G. wrote the manuscript; all authors discussed and edited the manuscript.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work was supported by the National Science Foundation under CHE-2142922 and generous start-up funds from the University of Washington. M.J.E. acknowledges the National Science Foundation Graduate Research Fellowship Program (DGE-2140004) for a graduate research fellowship. A.M.L. and M.N.P. acknowledge the University of Washington Clean Energy Institute for a graduate research fellowship. This material is based in part upon work supported by the state of Washington through the University of Washington Clean Energy Institute. NMR spectroscopy resources are supported under NIH S10 OD030224-01A1. We would also like to thank Morgan Skala for her assistance with setting up ball-mill grinding experiments.

Notes and references

- 1 A. Mandal and A. F. M. Kilbinger, *ACS Macro Lett.*, 2023, **12**, 1372–1378.
- 2 H. Liu, Y. Wang, W. Mo, H. Tang, Z. Cheng, Y. Chen, S. Zhang, H. Ma, B. Li and X. Li, *Adv. Func. Mater.*, 2020, **30**, 1910275.
- 3 S. S. Sheiko, B. S. Sumerlin and K. Matyjaszewski, *Prog. Polym. Sci.*, 2008, **33**, 759–785.
- 4 S. C. Radzinski, J. C. Foster, R. C. Jr. Chapleski, D. Troya and J. B. Matson, *J. Am. Chem. Soc.*, 2016, **138**, 6998–7004.
- 5 S. J. Scannelli, M. Alaboalirat, D. Troya and J. B. Matson, *Macromolecules*, 2023, **56**, 3838–3847.
- 6 R. Verduzco, X. Li, S. L. Pesek and G. E. Stein, *Chem. Soc. Rev.*, 2015, **44**, 2405–2420.
- 7 F. M. Haque and S. M. Grayson, *Nat. Chem.*, 2020, **12**, 433–444.
- 8 H. R. Kricheldorf, *J. Polym. Sci. A: Polym. Chem.*, 2010, **48**, 251–284.
- 9 T.-W. Wang and M. R. Golder, *Polym. Chem.*, 2021, **12**, 958–969.
- 10 T.-P. Lin, A. B. Chang, S.-X. L. Luo, H.-Y. Chen, B. Lee and R. H. Grubbs, *ACS Nano*, 2017, **11**, 11632–11641.
- 11 R. Liang, Q. Song, R. Li, A. N. Le, X. Fu, Y. Xue, X. Ji, W. Li and M. Zhong, *Angew. Chem. Int. Ed.*, 2022, **61**, e202210067.
- 12 K. Kawamoto, M. Zhong, K. R. Gadelrab, L.-C. Cheng, C. A. Ross, A. Alexander-Katz and J. A. Johnson, *J. Am. Chem. Soc.*, 2016, **138**, 11501–11504.
- 13 X. Li, S. L. Prukop, S. L. Biswal and R. Verduzco, *Macromolecules*, 2012, **45**, 7118–7127.
- 14 J. A. Johnson, Y. Y. Lu, A. O. Burts, Y. Xia, A. C. Durrell, D. A. Tirrell and R. H. Grubbs, *Macromolecules*, 2010, **43**, 10326–10335.
- 15 M. L. Ohnsorg, P. C. Prendergast, L. L. Robinson, M. R. Bockman, F. S. Bates and T. M. Reineke, *ACS Macro Lett.*, 2021, **10**, 375–381.
- 16 F. Vohidov, L. E. Milling, Q. Chen, W. Zhang, S. Bhagchandani, H. V.-T. Nguyen, D. J. Irvine and J. A. Johnson, *Chem. Sci.*, 2020, **11**, 5974–5986.
- 17 J. Liu, A. O. Burts, Y. Li, A. V. Zhukhovitskiy, M. F. Ottaviani, N. J. Turro and J. A. Johnson, *J. Am. Chem. Soc.*, 2012, **134**, 16337–16344.
- 18 A. L. Liberman-Martin, C. K. Chu and R. H. Grubbs, *Macromol. Rapid. Commun.*, 2017, **38**, 1700058.
- 19 A. L. Liberman-Martin, A. B. Chang, C. K. Chu, R. H. Siddique, B. Lee and R. H. Grubbs, *ACS Macro Lett.*, 2021, **10**, 1480–1486.
- 20 G. M. Miyake, V. A. Piunova, R. A. Weitekamp and R. H. Grubbs, *Angew. Chem. Int. Ed.*, 2012, **51**, 11246–11248.
- 21 G. M. Miyake, R. A. Weitekamp, V. A. Piunova and R. H. Grubbs, *J. Am. Chem. Soc.*, 2012, **134**, 14249–14254.

- 22 B. R. Sveinbjörnsson, R. A. Weitekamp, G. M. Miyake, Y. Xia, H. A. Atwater and R. H. Grubbs, *Proc. Natl. Acad. Sci.*, 2012, **109**, 14332–14336.
- 23 H. Gao and K. Matyjaszewski, *J. Am. Chem. Soc.*, 2007, **129**, 6633–6639.
- 24 M. Xie, J. Dang, H. Han, W. Wang, J. Liu, X. He and Y. Zhang, *Macromolecules*, 2008, **41**, 9004–9010.
- 25 Y. Xia, B. D. Olsen, J. A. Kornfield and R. H. Grubbs, *J. Am. Chem. Soc.*, 2009, **131**, 18525–18532.
- 26 N. Hadjichristidis, M. Pitsikalis, H. Iatrou and S. Pispas, *Macromol. Rapid. Commun.*, 2003, **24**, 979–1013.
- 27 O. M. Ogbra, N. C. Warner, D. J. O’Leary and R. H. Grubbs, *Chem. Soc. Rev.*, 2018, **47**, 4510–4544.
- 28 T.-L. Choi and R. H. Grubbs, *Angew. Chem. Int. Ed.*, 2003, **42**, 1743–1746.
- 29 Z.-H. Guo, A. N. Le, X. Feng, Y. Choo, B. Liu, D. Wang, Z. Wan, Y. Gu, J. Zhao, V. Li, C. O. Osuji, J. A. Johnson and M. Zhong, *Angew. Chem. Int. Ed.*, 2018, **57**, 8493–8497.
- 30 R. Liénard, J. De Winter and O. Coulembier, *J. Polym. Sci.*, 2020, **58**, 1481–1502.
- 31 M. Schappacher and A. Deffieux, *Science*, 2008, **319**, 1512–1515.
- 32 T.-W. Wang, P.-R. Huang, J. L. Chow, W. Kaminsky and M. R. Golder, *J. Am. Chem. Soc.*, 2021, **143**, 7314–7319.
- 33 C. W. Bielawski, D. Benitez and R. H. Grubbs, *Science*, 2002, **297**, 2041–2044.
- 34 Y. Xia, A. J. Boydston and R. H. Grubbs, *Angew. Chem. Int. Ed.*, 2011, **50**, 5882–5885.
- 35 K. Zhang and G. N. Tew, *ACS Macro Lett.*, 2012, **1**, 574–579.
- 36 D. Pal, Z. Miao, J. B. Garrison, A. S. Veige and B. S. Sumerlin, *Macromolecules*, 2020, **53**, 9717–9724.
- 37 Z. Miao, S. A. Gonsales, C. Ehm, F. Mentink-Vigier, C. R. Bowers, B. S. Sumerlin and A. S. Veige, *Nat. Chem.*, 2021, **13**, 792–799.
- 38 A. Narumi, M. Yamada, Y. Unno, J. Kumaki, W. H. Binder, K. Enomoto, M. Kikuchi and S. Kawaguchi, *ACS Macro Lett.*, 2019, **8**, 634–638.
- 39 D. Pal, J. B. Garrison, Z. Miao, L. E. Diodati, A. S. Veige and B. S. Sumerlin, *Macromolecules*, 2022, **55**, 7446–7453.
- 40 L. Xiao, L. Qu, W. Zhu, Y. Wu, Z. Liu and K. Zhang, *Macromolecules*, 2017, **50**, 6762–6770.
- 41 C. E. Wang, H. Wei, N. Tan, A. J. Boydston and S. H. Pun, *Biomacromolecules*, 2016, **17**, 69–75.
- 42 X.-Y. Tu, C. Meng, Y.-F. Wang, L.-W. Ma, B.-Y. Wang, J.-L. He, P.-H. Ni, X.-L. Ji, M.-Z. Liu and H. Wei, *Macromol. Rapid. Commun.*, 2018, **39**, 1700744.
- 43 J. Yang, R. Wang and D. Xie, *Macromolecules*, 2019, **52**, 7042–7051.
- 44 C. Chen, M. K. Singh, K. Wunderlich, S. Harvey, C. J. Whitfield, Z. Zhou, M. Wagner, K. Landfester, I. Lieberwirth, G. Fytas, K. Kremer, D. Mukherji, D. Y. W. Ng and T. Weil, *Nat. Commun.*, 2021, **12**, 3959.
- 45 A. Levenson, C. Morrison, P.-R. Huang, T.-W. Wang, Z. Carter-Schwendler and M. Golder, *ACS Macro Lett.*, 2023, **12**, 1286–1292.
- 46 R. W. Clarke, M. R. Caputo, L. Polo Fonseca, M. L. McGraw, L. T. Reilly, K. A. Franklin, A. J. Müller and E. Y.-X. Chen, *J. Am. Chem. Soc.*, 2024, **146**, 4930–4941.
- 47 M. L. McGraw, R. W. Clarke and E. Y.-X. Chen, *J. Am. Chem. Soc.*, 2021, **143**, 3318–3322.
- 48 C. Hu, E. Louisy, G. Fontaine and F. Bonnet, *J. Polym. Sci. A: Polym. Chem.*, 2017, **55**, 3175–3179.
- 49 S. Dutta, M. A. Wade, D. J. Walsh, D. Guironnet, S. A. Rogers and C. E. Sing, *Soft Matter*, 2019, **15**, 2928–2941.
- 50 J. Noh, M. B. Koo, J. Jung, G. I. Peterson, K. T. Kim and T.-L. Choi, *J. Am. Chem. Soc.*, 2023, **145**, 18432–18438.
- 51 J. Noh, G. I. Peterson and T.-L. Choi, *Angew. Chem. Int. Ed.*, 2021, **60**, 18651–18659.
- 52 G. I. Peterson, W. Ko, Y.-J. Hwang and T.-L. Choi, *Macromolecules*, 2020, **53**, 7795–7802.
- 53 Y. Liu, Y. Wu and F. Zhou, *Langmuir*, 2023, **39**, 37–44.
- 54 Z. Wang, L. Scheres, H. Xia and H. Zuilhof, *Adv. Func. Mater.* 2020, **30**, 1908098.
- 55 S. Mukherjee, R. Xie, V. G. Reynolds, T. Uchiyama, A. E. Levi, E. Valois, H. Wang, M. L. Chabinye and C. M. Bates, *Macromolecules*, 2020, **53**, 1090–1097.
- 56 V. G. Reynolds, S. Mukherjee, R. Xie, A. E. Levi, A. Atassi, T. Uchiyama, H. Wang, M. L. Chabinye and C. M. Bates, *Mater. Horiz.*, 2020, **7**, 181–187.
- 57 K. Zhang, M. A. Lackey, J. Cui and G. N. Tew, *J. Am. Chem. Soc.*, 2011, **133**, 4140–4148.
- 58 Y. Chen, Z. Fan, Y. Liu, Y. Wang, Z. Wang, R. Zhang, B. Ma, Y. Liu, W. Zhang, L. Tang and T. Sun, *Giant*, 2023, **15**, 100177.
- 59 D. Konar, V. K. Jakhar, K. A. Stewart, D. W. Lester, A. S. Veige and B. S. Sumerlin, *Macromolecules*, 2024, **57**, 1779–1787.
- 60 Y. Adeli, F. Owusu, F. A. Nüesch and D. M. Opris, *ACS Appl. Mater. Interfaces*, 2023, **15**, 20410–20420.
- 61 X. Yu, Y. Wang, M. Li, Y. Zhang, Y. Huang, Q. Qian, Y. Zheng, Q. Hou and X. Fan, *ACS Appl. Polym. Mater.*, 2023, **5**, 2750–2759.
- 62 P. Xu, S. Wang, A. Lin, H.-K. Min, Z. Zhou, W. Dou, Y. Sun, X. Huang, H. Tran and X. Liu, *Nat. Commun.*, 2023, **14**, 623.
- 63 B. R. Clarke, C. L. Witt, M. Ilton, A. J. Crosby, J. J. Watkins and G. N. Tew, *Angew. Chem. Int. Ed.*, 2024, **63**, e202318220.