

CONDENSED MATTER PHYSICS

Distinguishing surface and bulk electromagnetism via their dynamics in an intrinsic magnetic topological insulator

Khanh Duy Nguyen¹, Woojoo Lee^{1†}, Jianchen Dang², Tongyao Wu², Gabriele Berruto¹, Chenhui Yan¹, Chi Ian Jess Ip^{1‡}, Haoran Lin¹, Qiang Gao¹, Seng Huat Lee³, Binghai Yan⁴, Chaoxing Liu³, Zhiqiang Mao³, Xiao-Xiao Zhang², Shuolong Yang^{1*}

The indirect exchange interaction between local magnetic moments via surface electrons has been long predicted to bolster the surface ferromagnetism in magnetic topological insulators (MTIs), which facilitates the quantum anomalous Hall effect. This unconventional effect is critical to determining the operating temperatures of future topotronic devices. However, the experimental confirmation of this mechanism remains elusive, especially in intrinsic MTIs. Here, we combine time-resolved photoemission spectroscopy with time-resolved magneto-optical Kerr effect measurements to elucidate the unique electromagnetism at the surface of an intrinsic MTI MnBi_2Te_4 . Theoretical modeling based on 2D Ruderman-Kittel-Kasuya-Yosida interactions captures the initial quenching of a surface-rooted exchange gap within a factor of two but overestimates the bulk demagnetization by one order of magnitude. This mechanism directly explains the sizable gap in the quasi-2D electronic state and the nonzero residual magnetization in even-layer MnBi_2Te_4 . Furthermore, it leads to efficient light-induced demagnetization comparable to state-of-the-art magnetophotonic crystals, promising an effective manipulation of magnetism and topological orders for future topotronics.

INTRODUCTION

Bringing magnetism to the itinerant electronic states on the surface of three-dimensional (3D) topological insulators (TIs) is foundational to a variety of low-dimensional topological orders such as the quantum anomalous Hall insulators (1, 2) and axion insulators (3–5). The magnetism in 3D TIs can be established via Anderson-Goodenough-Kanamori superexchange (6, 7), valence electrons (Van Vleck paramagnetism) (8, 9), or magnetic proximity coupling (10). However, the unconventional Ruderman-Kittel-Kasuya-Yosida (RKKY) interaction on the material surface is exclusively required for the time-reversal (T) symmetry breaking on the topological surface states (TSSs) in magnetic TIs (MTIs) (2, 10–14). This mechanism has been predicted to enhance the surface ferromagnetism of 3D MTIs, where the itinerant Dirac fermions with vanishing Fermi momenta strongly favor ferromagnetic coupling between magnetic moments (11–17). The effect is further boosted when the magnetic moments are densely and uniformly distributed as in intrinsic MTIs. Thus, the 2D RKKY interaction fundamentally determines the size of the T -symmetry-broken energy gap, and, consequently, the temperature scale at which the low-dimensional topological orders can operate. A quantitative experimental revelation of the 2D RKKY interaction on the surface of intrinsic MTIs is of fundamental importance to the study of

low-dimensional topological orders and to the ultimate material engineering for applications at realistic temperatures.

Although there have been discussions of the RKKY interactions in several magnetically doped TI systems (18–20), the surface 2D RKKY interaction has not been observed directly and exclusively in intrinsic MTIs where the quantum anomalous Hall effect (QAHE) is expected to be realized at higher temperatures. Revealing this interaction in MTIs can be a substantial challenge using equilibrium spectroscopies, as magnetic interactions of various origins can all contribute to the overall magnetism (21). Here, we combine time- and angle-resolved photoemission spectroscopy (trARPES) and time-resolved magneto-optical Kerr effect (trMOKE) to reveal this distinct mechanism contributing to the surface magnetism in MnBi_2Te_4 (MBT), a platform on which the QAHE has been realized (2): A quasi-2D state (q -2DS) mediates the surface 2D RKKY interaction via p - d coupling on the top MBT layer. While trARPES resolves the dynamics of the exchange gap in the q -2DS with milli-electron volt-scale precisions, trMOKE observes the evolution of the magnetization with a dominant contribution from the bulk. Both quantities undergo a rapid quenching within 500 fs, suggesting the electronic nature of the demagnetization process. Layer-encoded frequency-domain ARPES on related $\text{MnBi}_{2n}\text{Te}_{3n+1}$ compounds (22) allows us to identify the surface nature of the q -2DS. We construct a 2D RKKY model involving localized Mn 3d moments and itinerant p electrons. The 2D RKKY framework not only accounts for the rapid quenching of the magnetization and the exchange gap but also provides a direct explanation for the considerably large exchange gap in the q -2DS. Furthermore, it can reconcile several open problems in intrinsic MTIs represented by MBT. These include the anomalously small gap at the Dirac point of the TSSs (23–27) and the nonzero residual magnetization in even-layer MBT (28, 29). Our work highlights the special magnetic interactions in the surface layer of MBT and establishes the physics foundation for effective

¹Pritzker School of Molecular Engineering, The University of Chicago, Chicago, IL 60637, USA. ²Department of Physics, University of Florida, Gainesville, FL 32611, USA. ³Department of Physics, Pennsylvania State University, University Park, PA 16802, USA. ⁴Department of Condensed Matter Physics, Weizmann Institute of Science, Rehovot 7610001, Israel.

*Corresponding author. Email: yangsl@uchicago.edu

†Present address: Quantum Technology Institute, Korean Research Institute of Standards and Science, Daejeon 34113, Republic of Korea.

‡Present address: Department of Physics, Massachusetts Institute of Technology, Cambridge, MA 02139, USA.

ultrafast manipulation of magnetism in tandem with topological orders through the p - d interactions.

RESULTS

MBT hosts A-type antiferromagnetism (AFM) with the Mn 3d moments ordered ferromagnetically within each septuple layer (SL) yet antiferromagnetically across adjacent SLs (Fig. 1A). The dynamics

of the electronic band structure upon optical excitation is shown in Fig. 1. The static ARPES spectrum in Fig. 1C displays the typical band structure of MBT. The Dirac point of the TSS remains gapless at all temperatures within our energy resolution. The second derivative plot in Fig. 1D clearly shows the splitting of the q -2DS near -0.2 eV (23, 26). These two bands merge into one once the temperature is elevated above the Néel temperature $T_N = 25$ K, as shown in Fig. 1E. The q -2DS band splitting is thus attributed to the magnetic

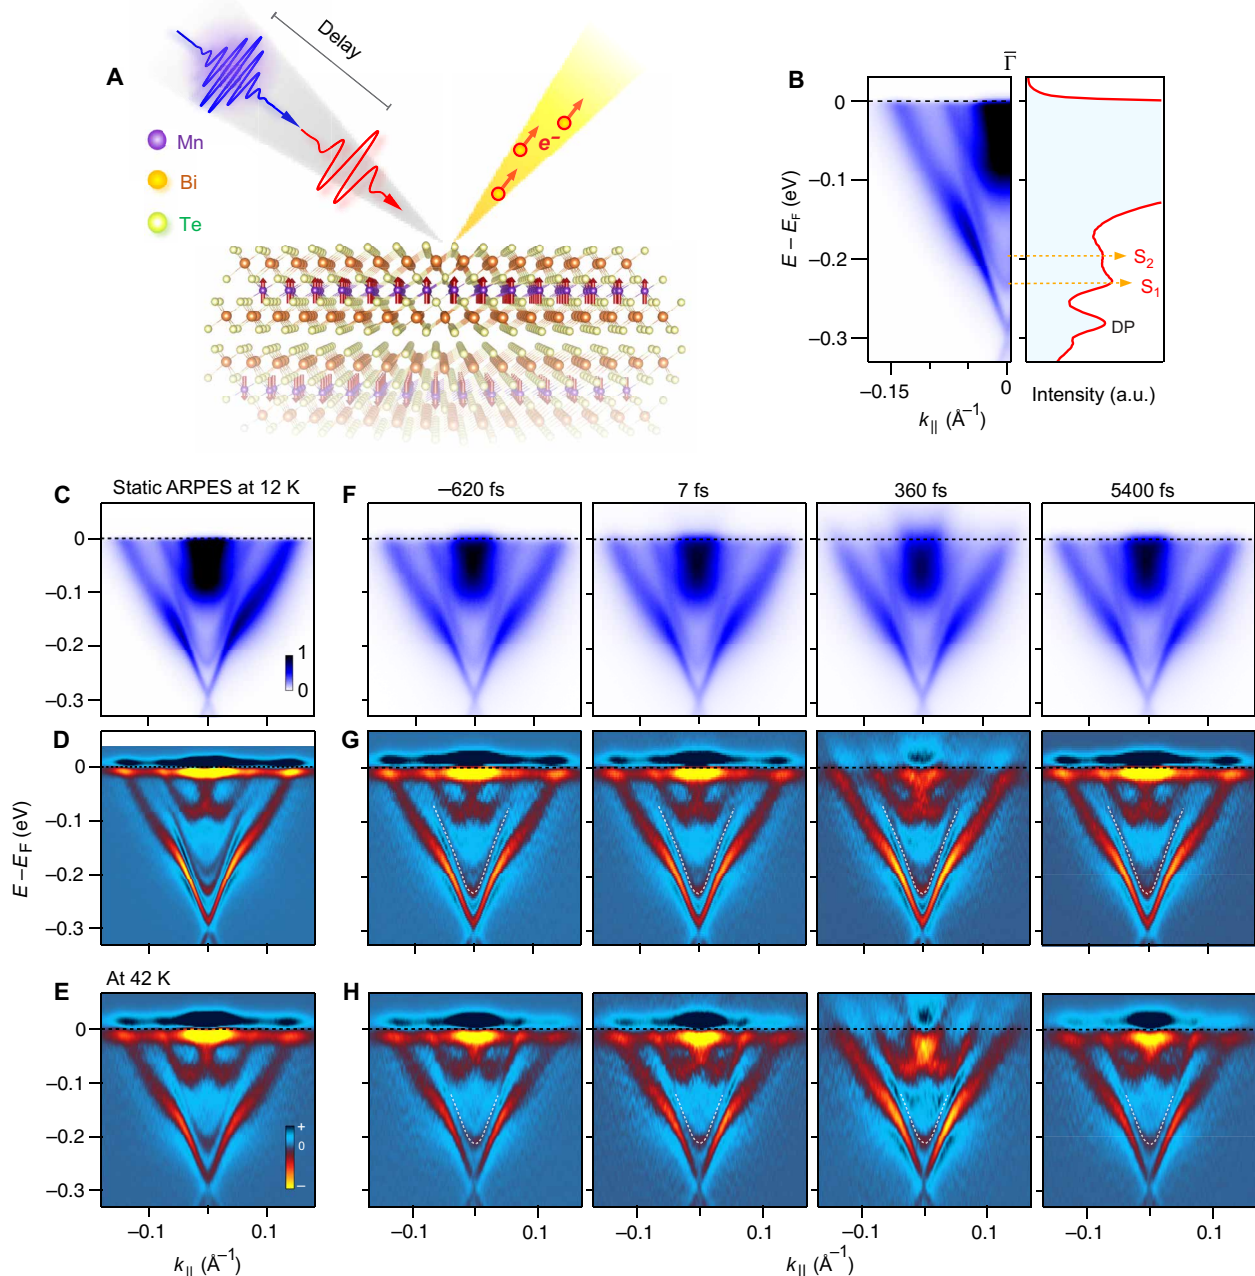


Fig. 1. Evolution of the electronic structure in MnBi₂Te₄ (MBT) resolved by trARPES. (A) Scheme of trARPES experiment on MBT. (B) The static ARPES spectrum of MBT along the $\bar{\Gamma}$ -K direction (left) and the energy distribution curve (EDC) taken at $\bar{\Gamma}$ (right) with quasi-2D sub-bands S_1 and S_2 and Dirac point marked. a.u., arbitrary units. (C) Full ARPES spectrum at 12 K. Second derivative plots at (D) 12 K and (E) 42 K are also shown. (F) Time-dependent ARPES spectra at select delays and the base temperature of 12 K for an incident pump fluence of $10 \mu\text{J}/\text{cm}^2$. Time-dependent, second-derivative spectra at (G) 12 K and (H) 42 K are also shown.

exchange interaction. The right panel of Fig. 1B displays the energy distribution curve (EDC) taken at $\bar{\Gamma}$, with the S_1 and S_2 peaks further illustrating the splitting of the q -2DS. The second derivative plot (Fig. 1D) also reveals a Rashba band splitting with the band bottom near -0.1 eV (24). These observations generally agree with the previous studies on MBT (23, 24). In this report, to study the interaction between the electronic and magnetic degrees of freedom, we focus on the evolution of the exchange gap of the q -2DS under optical excitation. Figure 1F displays the temporal evolution of the band structure upon 1.5-eV ultrafast optical excitation with an incident fluence of $10 \mu\text{J}/\text{cm}^2$ at the base temperature of 12 K. Because of the compromised energy resolution in trARPES (Materials and Methods) and of the transient spectral broadening, the S_1 - S_2 band splitting is less pronounced in the trARPES spectra. Meanwhile, second-derivative plots in Fig. 1G suggest the existence of band splitting at all delays. This is in stark contrast to the experimental results obtained at the base temperature of 42 K (Fig. 1H), where a single q -2DS is always identified. The comparison between Fig. 1G and Fig. 1H illustrates that optical excitation at 12 K

broadens the spectral features corresponding to the split q -2DS rather than completely destroying the magnetic exchange gap. On the other hand, the strong diffuse photoemission intensities prevent reliable quantification of an exchange gap in the Rashba states. However, its existence is suggested by the second-derivative maps of the trARPES spectra at 360 fs when the density curvature near E_F is suppressed. The dispersions revealed in the second-derivative map at 12 K (Fig. 1G) hint that a gap may open at the crossing points of the two split Rashba bands near -0.05 eV, compared to the data at 42 K (Fig. 1H).

To quantify the exchange gap at each time delay, we present a detailed analysis of the time-dependent EDCs taken at $k = 0$ in Fig. 2. We first focus on the EDCs taken at 12 K (solid balls in Fig. 2A). The EDC taken from the static ARPES spectrum exhibits two clear peaks near -0.23 and -0.19 eV, which correspond to the S_1 and S_2 bands marked in Fig. 1B. Similarly, time-dependent EDCs taken at -620 , 1380, and 5400 fs also exhibit two bumps corresponding to these two bands. We note that, at 7 and 360 fs, this two-bump feature may not be clearly identified. However, these EDCs are distinct from the

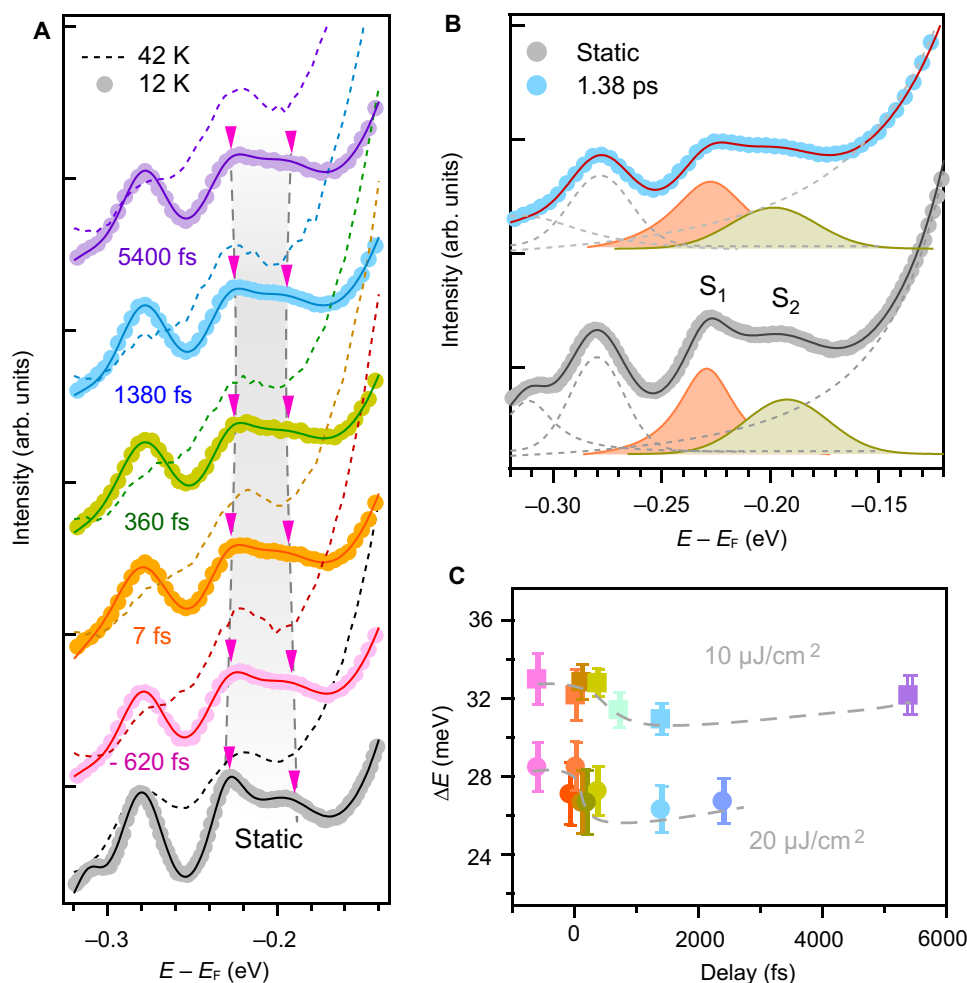


Fig. 2. Analysis of EDCs at the $\bar{\Gamma}$ point. (A) EDCs taken at $\bar{\Gamma}$ for select delays, with the pump fluence of $10 \mu\text{J}/\text{cm}^2$. Results for the base temperature of 12 K (solid balls) and 42 K (dashed lines) are directly compared. Solid curves denote the fit curves using a five-Lorentzian model to extract the exchange gap (pink triangles) at each delay. (B) Exemplary fits to the EDC taken with static ARPES (gray balls) and that with trARPES at the delay of 1.38 ps (blue balls). (C) Time-dependent exchange gaps between the S_1 and S_2 sub-bands for the IR fluences of 10 and $20 \mu\text{J}/\text{cm}^2$. The dashed lines are guides to the eyes. Error bars show one SD of uncertainty of the fitting.

counterparts taken at 42 K (dashed lines), which exhibit a clear single-peak feature near -0.22 eV. It appears that the position of this single q -2DS shifts to a slightly higher binding energy instead of residing in the middle between S_1 and S_2 . This is due to a slight doping change in the sample used for the higher-temperature measurements. Fitting the EDCs at 12 K to a five-Lorentzian model yields time-dependent exchange gaps shown in Fig. 2C. Notably, for pump fluences of 10 and $20 \mu\text{J}/\text{cm}^2$, the exchange gaps are transiently reduced by ~ 5 and $\sim 8\%$, respectively. This result shows that the functional shapes of the EDCs at 7 and 360 fs in the energy range of -0.17 to -0.25 eV are best understood as two broadened peaks corresponding to the S_1 and S_2 bands. Furthermore, because the exchange splitting gap between S_1 and S_2 is a manifestation of the magnetic ordering in MBT, our results give spectroscopic evidence that the magnetic subsystem is mildly affected using an infrared (IR) pump fluence of up to $20 \mu\text{J}/\text{cm}^2$. We notice that the gap values obtained in the trARPES experiment using an IR fluence of $20 \mu\text{J}/\text{cm}^2$ are consistently smaller than the corresponding ones using $10 \mu\text{J}/\text{cm}^2$ (Fig. 2C). This is due to the steady-state heating by the IR laser, resulting in an elevated sample temperature before time zero, which we estimate to be ~ 16 K for $10 \mu\text{J}/\text{cm}^2$ and ~ 21 K for $20 \mu\text{J}/\text{cm}^2$ (Supplementary Text S1). In contrast to previous trARPES studies (24, 30), our ultrahigh-quality trARPES experiment resolves the milli-electron volt-scale dynamical change of this magnetic exchange gap. This is due to a combination of ultrahigh crystal qualities, meticulously optimized time and energy resolutions, and a high signal-to-noise ratio enabling the detailed fitting analysis.

To compare the dynamics of the magnetic and electronic subsystems, we extract the transient electronic temperature (T_e) using trARPES and compare it with the magnetization measured by trMOKE. By integrating EDCs over the range of $[-0.2, 0.2] \text{ \AA}^{-1}$ along $\bar{\Gamma} - \bar{K}$, we obtain the overall electron population distribution of MBT near the Fermi level (E_F). After the initial electron-electron thermalization in the first 300 fs, the population distribution can be described by a modified Fermi-Dirac (FD) function, which allows us to extract T_e (fig. S1). Figure 3B summarizes the transient T_e for pump fluences of 10 and $20 \mu\text{J}/\text{cm}^2$. It reaches the peak values of 550 K for $20 \mu\text{J}/\text{cm}^2$ and 270 K for $10 \mu\text{J}/\text{cm}^2$, which are much higher than $T_N \sim 25$ K. Moreover, T_e relaxes to near the equilibrium value within ~ 2 ps, in contrast to a previous ultrafast electron diffuse scattering measurement reporting a significantly elevated T_e even after 10 ps (31). This difference can be understood by considering that the measurement in (31) used bulk-sensitive, 3.7-MeV electron beams, whereas our ARPES measurements use 6-eV photons and are relatively surface sensitive. The ultrafast dynamics of the magnetization is tracked by trMOKE (Fig. 3E). Notably, although trMOKE using 1.5-eV probe predominantly reflects the magnetic dynamics in the bulk, the initial demagnetization timescale of ~ 500 fs matches the onset timescale of T_e as resolved by surface-sensitive trARPES, indicating a connection between the conduction band electrons and magnetic interactions. We note that the higher pump fluences in trMOKE do not cause substantial lattice heating due to the much smaller laser illumination area with the focused $\sim 1.5\text{-}\mu\text{m}$ spot, which assists efficient thermal

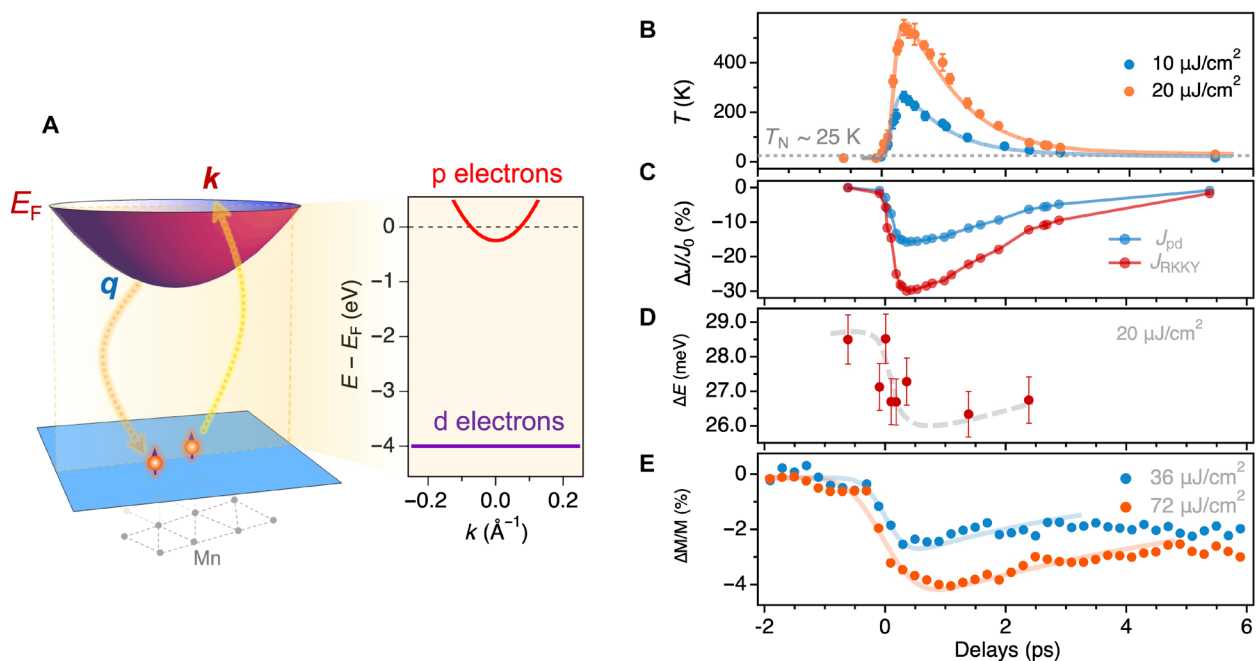


Fig. 3. Magnetic interactions in a 2D system with itinerant p electrons and localized Mn d electrons. (A) Illustration of an RKKY model that assumes the indirect interaction between localized d electrons via itinerant p electrons in two dimensions. (B) Transient electronic temperatures extracted by fitting the momentum-integrated EDC at each delay to a modified Fermi-Dirac (FD) function (Supplementary Text S1). Error bars show SD of the fitting. Solid curves denote simulation results using a microscopic Boltzmann model (Supplementary Text S2). The resulting p - d and RKKY coupling strengths are calculated and summarized in (C) based on the transient electronic temperature using a pump fluence of $20 \mu\text{J}/\text{cm}^2$. (D) Time-dependent exchange gap in the q -2DS also using the pump fluence of $20 \mu\text{J}/\text{cm}^2$. (E) Photoinduced demagnetization measured by trMOKE using a pump fluence of 36 and $72 \mu\text{J}/\text{cm}^2$. Solid lines indicate the fitting curves using an exponential decay convolved with a Gaussian function.

relaxation into colder regions. This is also verified by the temperature dependence of reflective magnetic circular dichroism (RMCD) when using the pulsed laser as the excitation source, with similar fluences and pulse conditions as used in trMOKE, that shows the expected magnetic transition (fig. S9). While the direct 3d electronic transition occurs at a higher energy compared to the 1.5-eV probe light, optical spectroscopies using <2-eV photons still reflect the Mn magnetic moments (29, 32). In particular, the optical Kerr signal has contributions from both the real and imaginary parts of the dielectric function. The real part contains a broad response from excitations at all frequencies and, therefore, the higher-energy 3d transitions (33, 34). The applied external magnetic field (1 T) in our trMOKE measurements does not change the AFM ground state of MBT (29, 35), and, thus, the revealed demagnetization dynamics is intrinsic to the material.

We clarify the origin of the q -2DS by looking into existing studies in the literature. First, static ARPES studies suggested that the q -2DS in MBT evolves into a pair of Rashba-split states in $\text{MnBi}_{2n}\text{Te}_{3n+1}$ superlattices, with the binding energy systematically increased as a function of the superlattice order n (22, 23). Second, our previous study using layer-encoded, frequency-domain ARPES on MnBi_4Te_7 elucidated that these q -2DSs are mostly spatially confined to the top MBT layer, based on the selective coupling between the q -2DS and the MBT-derived A_{1g} phonon (22). Notably, the timescale of the T_e relaxation of the q -2DS in $\text{MnBi}_2\text{Te}_4/(\text{Bi}_2\text{Te}_3)_n$ thin films is similar to that in MBT single crystals but substantially different from that in Bi_2Te_3 films (Supplementary Text S3). This observation further corroborates the literature on the fact that the q -2DS of MBT single crystals is predominantly localized in the top MBT layer. This layer origin implies that the q -2DS is only sensitive to ferromagnetic ordering in the top layer, which reconciles the sizable exchange gap as seen in Figs. 1 and 2.

The insight of the spatial location of the q -2DS renders the top layer of MBT a unique system for magnetic interactions: The q -2DS effectively mediates the indirect exchange interaction between the Mn 3d local moments in a 2D layer, which is, by definition, the 2D RKKY interaction (36–38). In addition, previous ARPES studies (24, 39) have resolved a 30-meV exchange gap in the Rashba-split states at the binding energy of nearly 0.1 eV, suggesting that these states also contribute to the RKKY interactions. One should note that other interaction channels such as Anderson-Goodenough-Kanamori superexchange via p - d orbital mixing (6, 7) and the Van Vleck mechanism via the valence electrons (8, 9) must not be neglected for the full picture of magnetism in MBT. In our study, we focus on the ultrafast processes driven by the excitation of conduction electrons, leading to a transient change of the 2D RKKY interaction.

To elucidate the role of RKKY physics in this system, we set up a 2D RKKY model for the topmost SL of MBT, as illustrated in Fig. 3A. Taking into account the available ARPES data, we assume a nearly free-electron-like conduction band of Bi- p and Te- p characters while fixing the dispersion-less d electrons to the binding energy of 4 eV (40). This is a simplification of the MBT system, as both the q -2DS and the Rashba-split states contribute to the RKKY interaction. In this model, the effective magnetic Hamiltonian is

$$H_{\text{RKKY}} = \sum_{i \neq j} \mathfrak{J}_{ij} \mathbf{S}_i \cdot \mathbf{S}_j \quad (1)$$

Here, the RKKY coupling constant $\mathfrak{J}_{ij}$ between the magnetic moments $\mathbf{S}_i$ and $\mathbf{S}_j$ at the lattice sites $\mathbf{r}_i$ and $\mathbf{r}_j$, respectively, is formulated as follows (41–43)

$$\mathfrak{J}_{ij} = - \left[\frac{J(T)}{N} \right]^2 \sum_{\mathbf{k}, \mathbf{q}} \cos[(\mathbf{k} - \mathbf{q}) \cdot (\mathbf{r}_i - \mathbf{r}_j)] \frac{n_{\mathbf{k}} - n_{\mathbf{q}}}{\varepsilon_{\mathbf{q}} - \varepsilon_{\mathbf{k}}} \quad (2)$$

where N is the number of lattice sites; $\mathbf{k}$ and $\mathbf{q}$ are the momenta of p electrons; function n represents the occupation number of an electronic state where ε is the corresponding binding energy. We let $n_{\mathbf{k}}$ follow the FD statistics with a double degeneracy, which contributes to the temperature dependence of the formalism. The Kondo coupling constant J defines the coupling strength J_{pd} between the p and d electrons (44), which directly corresponds to the exchange gap in the conduction band observed by ARPES. As MBT is a cooperative magnetic system, the formation of Kondo singlets is excluded (45). Therefore, it is possible to use Anderson's Poor-Man scaling approach (43–46) to track the evolution of this p - d coupling strength $J_{pd}(T)$ with respect to the electronic temperature

$$J_{pd}(T) \equiv \rho J(T) \approx \rho J + 2(\rho J)^2 \ln\left(\frac{D}{T}\right) + \mathcal{O}[(\rho J)^3] \quad (3)$$

in which ρ is the density of states of the conduction band and D is the corresponding half bandwidth (Supplementary Text S4). Last, the total temperature dependency of the RKKY coupling strength becomes

$$J_{\text{RKKY}}(T) \propto \sum_{i \neq j} - \left(\frac{J_{pd}(T)}{N} \right)^2 \sum_{\mathbf{k}, \mathbf{q}} \cos[(\mathbf{k} - \mathbf{q}) \cdot (\mathbf{r}_i - \mathbf{r}_j)] \frac{n_{\mathbf{k}} - n_{\mathbf{q}}}{\varepsilon_{\mathbf{q}} - \varepsilon_{\mathbf{k}}} \quad (4)$$

The calculated results show that the temporal evolution of J_{pd} and J_{RKKY} closely follow that of the transient electronic temperature (Fig. 3C). The negative values of J_{RKKY} support the ferromagnetic ground state of MBT in a single SL (Supplementary Text S4). We note that the RKKY interaction can also be viewed as the weak-coupling limit of the generic p - d exchange mechanism of ferromagnetism in dilute magnetic semiconductors (47).

A direct comparison of the temporal evolutions of J_{pd} and J_{RKKY} with that of the exchange gap (Fig. 3D) and that of magnetization (Fig. 3E) elucidates the RKKY physics right after time zero. All four quantities reach their minima within the first 500 to 1000 fs. This fast response resembles that in 2D metallic ferromagnets Fe_xGeTe_2 ($x = 3$ to 5) (48–50) and differs from the slower demagnetization normally seen in 2D ferromagnetic insulators at the low fluence limit, where RKKY coupling is generally unavailable (51). Theoretically, J_{pd} is proportional to the exchange gap (52). The 16% maximum reduction of the calculated J_{pd} is twice the maximum reduction of the exchange gap observed by trARPES (~8%). However, in this model, we use the overall spectral width of the Mn 3d band to estimate the bare resonant width Δ (Supplementary Text S4). This is likely an overestimation of Δ due to extrinsic contributions to the spectral width such as electron-impurity scattering, which may subsequently lead to an exaggeration of the transient reduction of J_{pd} . Considering these complications and the large uncertainties in the observed gap dynamics, we conclude that the 2D RKKY model sufficiently describes the initial quenching of the exchange gap in the q -2DS. Meanwhile, J_{RKKY} is theoretically connected to the magnetization measured by trMOKE, but the connection is less straightforward. The calculated J_{RKKY} is reduced by 30% under the

IR fluence of $20 \mu\text{J}/\text{cm}^2$. Assuming that the 2D RKKY interaction is the only magnetic interaction in the Weiss model for ferromagnetism, this leads to $\sim 10\%$ reduction in the magnetization (Supplementary Text S5). However, using the linear fluence dependence of the demagnetization magnitude in trMOKE (fig. S8) and considering the different pumping and probing depths in trARPES and trMOKE, we obtain $\sim 1.9\%$ demagnetization in the trMOKE experiment for the same absorbed energy density as used in trARPES (Supplementary Text S5). Even after this proper normalization, the demagnetization magnitude from trMOKE is still one order of magnitude smaller than the theoretical prediction, which can be understood as follows. The magnetic dynamics probed by trMOKE using 1.5-eV light reflects magnetic interactions predominantly in the bulk. The substantial difference between the theoretical and experimental demagnetization percentages suggests that RKKY interactions make a much smaller contribution to the bulk magnetic order of MBT, as compared to the surface of MBT that hosts the q -2DS to mediate the surface RKKY coupling. Instead, superexchange and Van Vleck mechanisms can be the more dominant channels in the bulk and are mostly T_e independent in sub-picosecond dynamics (Supplementary Text S5) (8, 53). At later time (>1 ps), the calculated coupling constants quickly return to the equilibrium values following the T_e dynamics, yet the experimental exchange gap and magnetization exhibit prolonged relaxation dynamics (fig. S11). This reflects the delayed lattice heating and its impact on the orbital overlap in the superexchange interaction (53).

DISCUSSION

We have used a 2D RKKY model to successfully account for the initial demagnetization timescale as well as the order of magnitude for the exchange gap quenching. Notably, the combination of trARPES and trMOKE experiments confines the theoretical picture. We have also considered the Elliott-Yafet-type spin-flip model, which is widely used for metallic ferromagnets (54). Using our experimental transient T_e and material parameters in the literature (31, 54, 55) as inputs, this model would lead to 100% demagnetization, which is inconsistent with either our trARPES or trMOKE results (Supplementary Text S6). Another theoretical framework widely adopted by studies on 2D magnets is the Landau-Lifshitz-Gilbert model (31, 49, 51), in which the leading terms can be equivalent to the RKKY Hamiltonian if explicitly incorporating the p - d interactions (Supplementary Text S7) (31). The success of the 2D RKKY model in explaining the timescale and magnitude of the exchange gap reduction also corroborates the fact that the q -2DS resides predominantly on the top layer of MBT. The formation of the q -2DS can be fundamentally driven by surface defects (56). The same defects can lead to the relocation of the TSS into the space between the first and second SLs (57). The opposite magnetic moments from the first and second SLs may give rise to a vanishing T -symmetry-broken gap on the TSS. This hints to a direction for future designs of high- T_c QAHE, in which the TSSs should be spatially confined to the top SL by mitigating the surface defects via chemical or thermal treatments to enhance the interaction with the magnetism.

Moreover, the additional RKKY interactions mediated by the q -2DS suggest that the surface SL is magnetically inequivalent to the interior SLs. In ultrathin MBT flakes, the electronic structure at the top vacuum/MBT interface is expected to be different from

that at the bottom MBT/substrate interface, giving rise to disparate magnetic interactions on the top and bottom surfaces. This may lead to an inversion symmetry breaking and, thus, provide an explanation for the residual magnetization at zero field and the hysteresis loop in even-layer MBT, characterized by RMCD (29, 32) and anomalous Hall effect measurements (28, 58). As the external field is scanned toward 0 T, the surface magnetization boosted by the 2D RKKY interactions on the top surface may not be compensated by that on the bottom surface, leading to an overall residual magnetization.

The 2D RKKY mechanism suggests a unique path for effective magnetic manipulation through the surface electrons, which can be relevant for future device applications. First, 2D electronic systems generally have weak dielectric screening, leading to enhanced interactions between electromagnetic fields and individual charge carriers (59). This aspect, together with the miniscule electronic heat capacity due to the small Fermi surfaces, gives rise to an effective electronic heating to a peak temperature > 500 K even using a mild fluence of $20 \mu\text{J}/\text{cm}^2$. Furthermore, in MBT, the absorbed energy is rapidly transferred to the magnetic system through the d - p interaction (see Fig. 4 for a comparison with other magnets). The efficiency of modulating the magnetism in MBT, characterized by the percentage of magnetization changes normalized by the incident fluence, is higher than those of many common magnets (60–71) and comparable to that of engineered magnetophotonic crystals (66). This accelerated channel of energy transfer from optical excitation to magnetic subsystems in MBT is particularly beneficial in applications such as optoelectronics and magnetic memories toward the 2D limit. Moreover, MBT is an MTI where the magnetism and topology of the electronic structure are mutually locked. Recently, the axion optical induction of antiferromagnetic domains has been demonstrated in even-layer MBT flakes (72). Here, the revealed 2D RKKY interaction can be involved in this process and can potentially facilitate a more energy-efficient optoelectronic switching of both even-layer and odd-layer MBT flakes using circularly polarized light. This special property can seed the development of topological spintronics based on edge-state chirality switching (73, 74) using ultrafast optical excitations.

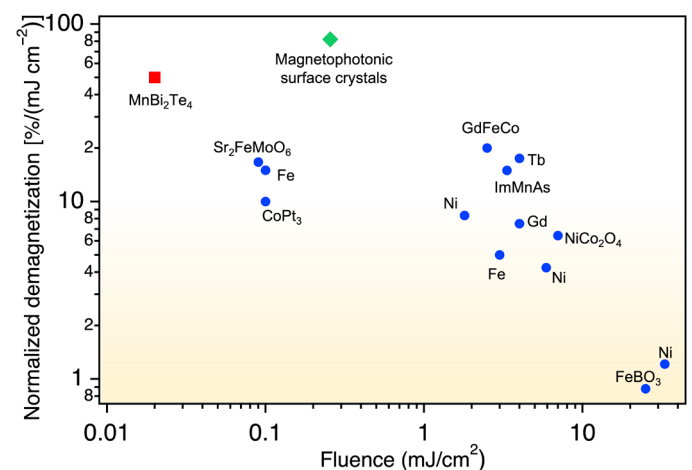


Fig. 4. Summary of the percentages of demagnetization normalized by incident pump fluences, measured by trMOKE on MBT and some common magnets. Data points other than that of MBT are taken from (60–71).

MATERIALS AND METHODS

Sample growth

The MBT single crystals were grown using a self-flux method (75). The mixtures of high-purity manganese powder (99.95%), bismuth shot (99.999%), and tellurium ingot (99.9999+%) with the molar ratio of Mn:Bi:Te = 1:10:16 are heated up to 900°C for 12 hours to promote homogeneous melting and slowly cooled down (1.5°C/hour) to a temperature within the 590° to 630°C range, followed by centrifugation to remove excess flux. The MBT single crystals were cleaved in situ under a pressure $< 5 \times 10^{-11}$ mbar for the ARPES measurements.

The thin-film materials $(\text{MnBi}_2\text{Te}_4)/(\text{Bi}_2\text{Te}_3)_{30}$ and $(\text{Bi}_2\text{Te}_3)_{27}$ (Supplementary Text S3) were grown by molecular beam epitaxy (MBE) using 99.9998% Mn, 99.999% Bi, and 99.9999% Te. Bi_2Te_3 films were grown on 0.05 wt % Nb-doped SrTiO_3 (111) substrates at 240°C with a Bi:Te flux ratio of 1:16. The MBT top layer was formed by depositing MnTe on top of Bi_2Te_3 and annealed at 270°C in a Te-rich atmosphere. The films were then transferred in situ to the ARPES chamber for measurements.

ARPES measurements

The static and trARPES measurements were performed on the multi-resolution photoemission spectroscopy platform at the University of Chicago (76). The 6-eV laser for static ARPES was generated from a mode-locked Ti:sapphire oscillator with a repetition rate of 80 MHz. The trARPES setup featured a 200-kHz Yb:KGW laser accompanied by noncollinear optical parametric amplifiers to produce ultrafast 1.5-eV IR pump pulses and 6-eV ultraviolet probe pulses. The energy resolutions of the static and trARPES setups were better than 4 and 20 meV, respectively. Focused probe beam waists, as characterized by the full width at half maximum, were 14 μm by 20 μm and 34 μm by 53 μm for the static and trARPES experiments, respectively. A systematic alignment procedure was adopted to ensure the overlap of the probed regions for static and trARPES (22). The linearly polarized, $\sim 110 \mu\text{m}$ -by- $140 \mu\text{m}$ -sized, ~ 20 -fs-long IR pump pulses were dimmed to incident fluences of 20 $\mu\text{J}/\text{cm}^2$ and below. The time resolution was determined to be ~ 150 fs, limited by the duration of the probe pulses.

trMOKE measurements

Steady-state RMCD measurements were done with 1.95-eV continuous-wave laser and with the pulsed 1.55-eV Ti:sapphire output (Coherent Chameleon), respectively. The light beam was modulated at 50 kHz between the left and right circular polarization using a Hinds photoelastic modulator. The reflected light was focused onto a photodiode. The magnetic circular dichroism was determined as the ratio of the ac component of the photodiode signal measured by a lock-in amplifier at the polarization modulation frequency and the dc component of the photodiode signal measured by a voltmeter. In trMOKE, the probe beam was the output of the Ti:sapphire laser at 1.55 eV, and the pump beam was the second harmonic of a Coherent Compact optical parametric oscillator at 1.88 eV. The time delay between the pump and probe pulses was controlled by a motorized linear delay stage, and the pump was modulated with a mechanical chopper. The reflected probe light passed through a half-wave Fresnel rhomb and a Wollaston prism and detected by a balanced photodiodes locked at the chopper frequency. The pump light spot diameter was around 1.5 μm . The optical measurements were done on

a ~ 100 -nm-thick sample flake on a SiO_2/Si substrate in a microscopic optical cryostat (attoDry 1000) with a base temperature of 3.5 K and a superconducting solenoid magnet up to 9 T.

Supplementary Materials

This PDF file includes:

Supplementary Text S1 to S7

Figs. S1 to S11

References

Correction (16 September 2024): Due to an error introduced during the copyediting process, two instances of meV were incorrectly expanded as “mega-electron volt.” These have been corrected to “milli-electron volt.” The PDF and XML have been updated.

REFERENCES AND NOTES

1. C.-Z. Chang, J. Zhang, X. Feng, J. Shen, Z. Zhang, M. Guo, K. Li, Y. Ou, P. Wei, L. L. Wang, Z. Q. Ji, Y. Feng, S. Ji, X. Chen, J. Jia, X. Dai, Z. Fang, S. C. Zhang, K. He, Y. Wang, L. Lu, X. C. Ma, Q. K. Xue, Experimental observation of the quantum anomalous hall effect in a magnetic topological insulator. *Science* **340**, 167–170 (2013).
2. Y. Deng, Y. Yu, M. Z. Shi, Z. Guo, Z. Xu, J. Wang, X. H. Chen, Y. Zhang, Quantum anomalous Hall effect in intrinsic magnetic topological insulator MnBi_2Te_4 . *Science* **367**, 895–900 (2020).
3. X.-L. Qi, T. L. Hughes, S.-C. Zhang, Topological field theory of time-reversal invariant insulators. *Phys. Rev. B* **78**, 195424 (2008).
4. F. Wilczek, Two applications of axion electrodynamics. *Phys. Rev. Lett.* **58**, 1799–1802 (1987).
5. C. Liu, Y. Wang, H. Li, Y. Wu, Y. Li, J. Li, K. He, Y. Xu, J. Zhang, Y. Wang, Robust axion insulator and Chern insulator phases in a two-dimensional antiferromagnetic topological insulator. *Nat. Mater.* **19**, 522–527 (2020).
6. C.-Z. Chang, C.-X. Liu, A. H. MacDonald, Colloquium: Quantum anomalous Hall effect. *Rev. Mod. Phys.* **95**, 011002 (2023).
7. C. Śliwa, C. Autieri, J. A. Majewski, T. Dietl, Superexchange dominates in magnetic topological insulators. *Phys. Rev. B* **104**, L220404 (2021).
8. J. H. Van Vleck, On dielectric constants and magnetic susceptibilities in the new quantum mechanics part III—Application to dia- and paramagnetism. *Phys. Rev.* **31**, 587–613 (1928).
9. R. Yu, W. Zhang, H. J. Zhang, S. C. Zhang, X. Dai, Z. Fang, Quantized anomalous Hall effect in magnetic topological insulators. *Science* **329**, 61–64 (2010).
10. R. Watanabe, R. Yoshimi, M. Kawamura, M. Mogi, A. Tsukazaki, X. Z. Yu, K. Nakajima, K. S. Takahashi, M. Kawasaki, Y. Tokura, Quantum anomalous Hall effect driven by magnetic proximity coupling in all-telluride based heterostructure. *Appl. Phys. Lett.* **115**, 102403 (2019).
11. Q. Liu, C. X. Liu, C. Xu, X. L. Qi, S. C. Zhang, Magnetic impurities on the surface of a topological insulator. *Phys. Rev. Lett.* **102**, 156603 (2009).
12. J. Wang, B. Lian, S.-C. Zhang, Quantum anomalous Hall effect in magnetic topological insulators. *Phys. Scr.* **T164**, 014003 (2015).
13. D. Pesin, A. H. MacDonald, Spintronics and pseudospintronics in graphene and topological insulators. *Nat. Mater.* **11**, 409–416 (2012).
14. D. K. Efimkin, V. Galitski, Self-consistent theory of ferromagnetism on the surface of a topological insulator. *Phys. Rev. B* **89**, 115431 (2014).
15. D. A. Abanin, D. A. Pesin, Ordering of magnetic impurities and tunable electronic properties of topological insulators. *Phys. Rev. Lett.* **106**, 136802 (2011).
16. J.-J. Zhu, D. X. Yao, S. C. Zhang, K. Chang, Electrically controllable surface magnetism on the surface of topological insulators. *Phys. Rev. Lett.* **106**, 097201 (2011).
17. R. R. Biswas, A. V. Balatsky, Impurity-induced states on the surface of three-dimensional topological insulators. *Phys. Rev. B* **81**, 233405 (2010).
18. J. G. Checkelsky, J. Ye, Y. Onose, Y. Iwasa, Y. Tokura, Dirac-fermion-mediated ferromagnetism in a topological insulator. *Nat. Phys.* **8**, 729–733 (2012).
19. P. Sessi, F. Reis, T. Bathon, K. A. Kokh, O. E. Tereshchenko, M. Bode, Signatures of Dirac fermion-mediated magnetic order. *Nat. Commun.* **5**, 5349 (2014).
20. X. Kou, L. He, M. Lang, Y. Fan, K. Wong, Y. Jiang, T. Nie, W. Jiang, P. Upadhyaya, Z. Xing, Y. Wang, F. Xiu, R. N. Schwartz, K. L. Wang, Manipulating surface-related ferromagnetism in modulation-doped topological insulators. *Nano Lett.* **13**, 4587–4593 (2013).
21. W. Wang, Y. Ou, C. Liu, Y. Wang, K. He, Q. K. Xue, W. Wu, Direct evidence of ferromagnetism in a quantum anomalous Hall system. *Nat. Phys.* **14**, 791–795 (2018).
22. W. Lee, S. Fernandez-Mulligan, H. Tan, C. Yan, Y. Guan, S. H. Lee, R. Mei, C. Liu, B. Yan, Z. Mao, S. Yang, Layer-by-layer disentanglement of Bloch states. *Nat. Phys.* **19**, 950–955 (2023).
23. C. Yan, S. Fernandez-Mulligan, R. Mei, S. H. Lee, N. Protic, R. Fukumori, B. Yan, C. Liu, Z. Mao, S. Yang, Origins of electronic bands in the antiferromagnetic topological insulator MnBi_2Te_4 . *Phys. Rev. B* **104**, L041102 (2021).

24. D. Nevola, H. X. Li, J. Q. Yan, R. G. Moore, H. N. Lee, H. Miao, P. D. Johnson, Coexistence of surface ferromagnetism and a gapless topological state in MnBi_2Te_4 . *Phys. Rev. Lett.* **125**, 117205 (2020).
25. Y.-J. Hao, P. Liu, Y. Feng, X. M. Ma, E. F. Schiwer, M. Arita, S. Kumar, C. Hu, R. Lu, M. Zeng, Y. Wang, Z. Hao, H. Y. Sun, K. Zhang, J. Mei, N. Ni, L. Wu, K. Shimada, C. Chen, Q. Liu, C. Liu, Gapless surface Dirac cone in antiferromagnetic topological insulator MnBi_2Te_4 . *Phys. Rev. X* **9**, 041038 (2019).
26. Y. J. Chen, L. X. Xu, J. H. Li, Y. W. Li, H. Y. Wang, C. F. Zhang, H. Li, Y. Wu, A. J. Liang, C. Chen, S. W. Jung, C. Cacho, Y. H. Mao, S. Liu, M. X. Wang, Y. F. Guo, Y. Xu, Z. K. Liu, L. X. Yang, Y. L. Chen, Topological electronic structure and its temperature evolution in antiferromagnetic topological insulator MnBi_2Te_4 . *Phys. Rev. X* **9**, 041040 (2019).
27. M. M. Otrokov, I. I. Klimovskikh, H. Bentmann, D. Estyunin, A. Zeugner, Z. S. Aliev, S. Gaß, A. U. B. Wolter, A. V. Koroleva, A. M. Shikin, M. Blanco-Rey, M. Hoffmann, I. P. Rusinov, A. V. Vyazovskaya, S. V. Eremeev, Y. M. Koroteev, V. M. Kuznetsov, F. Freyse, J. Sánchez-Barriga, I. R. Amiraslanov, M. B. Babanly, N. T. Mamedov, N. A. Abdullayev, V. N. Zverev, A. Alfonsov, V. Kataev, B. Büchner, E. F. Schiwer, S. Kumar, A. Kimura, L. Petaccia, G. di Santo, R. C. Vidal, S. Schatz, K. Kißner, M. Ünzelmann, C. H. Min, S. Moser, T. R. F. Peixoto, F. Reinert, A. Ernst, P. M. Echenique, A. Isaeva, E. V. Chulkov, Prediction and observation of an antiferromagnetic topological insulator. *Nature* **576**, 416–422 (2019).
28. Y.-F. Zhao, L. J. Zhou, F. Wang, G. Wang, T. Song, D. Ovchinnikov, H. Yi, R. Mei, K. Wang, M. H. W. Chan, C. X. Liu, X. Xu, C. Z. Chang, Even-odd layer-dependent anomalous Hall effect in topological magnet MnBi_2Te_4 thin films. *Nano Lett.* **21**, 7691–7698 (2021).
29. S. Yang, X. Xu, Y. Zhu, R. Niu, C. Xu, Y. Peng, X. Cheng, X. Jia, Y. Huang, X. Xu, J. Lu, Y. Ye, Odd-even layer-number effect and layer-dependent magnetic phase diagrams in MnBi_2Te_4 . *Phys. Rev. X* **11**, 011003 (2021).
30. P. E. Majchrzak, Y. Liu, K. Volckaert, D. Biswas, C. Sahoo, D. Puntel, W. Bronsch, M. Tuniz, F. Cilento, X. C. Pan, Q. Liu, Y. P. Chen, S. Ulstrup, Van der Waals engineering of ultrafast carrier dynamics in magnetic heterostructures. *Nano Lett.* **23**, 414–421 (2023).
31. H. Padmanabhan, V. A. Stoica, P. K. Kim, M. Poore, T. Yang, X. Shen, A. H. Reid, M. F. Lin, S. Park, J. Yang, H. H. Wang, N. Z. Koocher, D. Puggioni, A. B. Georgescu, L. Min, S. H. Lee, Z. Mao, J. M. Rondinelli, A. M. Lindenberg, L. Q. Chen, X. Wang, R. D. Averitt, J. W. Freeland, V. Gopalan, Large exchange coupling between localized spins and topological bands in MnBi_2Te_4 . *Adv. Mater.* **34**, e2202841 (2022).
32. D. Ovchinnikov, X. Huang, Z. Lin, Z. Fei, J. Cai, T. Song, M. He, Q. Jiang, C. Wang, H. Li, Y. Wang, Y. Wu, D. Xiao, J. H. Chu, J. Yan, C. Z. Chang, Y. T. Cui, X. Xu, Intertwined topological and magnetic orders in atomically thin Chern insulator MnBi_2Te_4 . *Nano Lett.* **21**, 2544–2550 (2021).
33. M. Wu, Z. Li, T. Cao, S. G. Louie, Physical origin of giant excitonic and magneto-optical responses in two-dimensional ferromagnetic insulators. *Nat. Comm.* **10**, 2371 (2019).
34. J. Ahn, S.-Y. Xu, A. Vishwanath, Theory of optical axion electrodynamics and application to the Kerr effect in topological antiferromagnets. *Nat. Comm.* **13**, 7615 (2022).
35. J. Cai, D. Ovchinnikov, Z. Fei, M. He, T. Song, Z. Lin, C. Wang, D. Cobden, J. H. Chu, Y. T. Cui, C. Z. Chang, D. Xiao, J. Yan, X. Xu, Electric control of a canted-antiferromagnetic Chern insulator. *Nat. Comm.* **13**, 1668 (2022).
36. M. A. Ruderman, C. Kittel, Indirect exchange coupling of nuclear magnetic moments by conduction electrons. *Phys. Rev.* **96**, 99–102 (1954).
37. T. Kasuya, A theory of metallic ferro- and antiferromagnetism on Zener's model. *Prog. Theor. Phys.* **16**, 45–57 (1956).
38. K. Yosida, Magnetic properties of Cu-Mn alloys. *Phys. Rev.* **106**, 893–898 (1957).
39. D. A. Estyunin, I. I. Klimovskikh, A. M. Shikin, E. F. Schiwer, M. M. Otrokov, A. Kimura, S. Kumar, S. O. Filnov, Z. S. Aliev, M. B. Babanly, E. V. Chulkov, Signatures of temperature driven antiferromagnetic transition in the electronic structure of topological insulator MnBi_2Te_4 . *APL Mat.* **8**, 021105 (2020).
40. R. C. Vidal, H. Bentmann, T. R. F. Peixoto, A. Zeugner, S. Moser, C.-H. Min, S. Schatz, K. Kißner, M. Ünzelmann, C. I. Fornari, H. B. Vasili, M. Valvidares, K. Sakamoto, D. Mondal, J. Fujii, I. Vobornik, S. Jung, C. Cacho, T. K. Kim, R. J. Koch, C. Jozwiak, A. Bostwick, J. D. Denlinger, E. Rotenberg, J. Buck, M. Hoesch, F. Diekmann, S. Rohlf, M. Kalläne, K. Rossnagel, M. M. Otrokov, E. V. Chulkov, M. Ruck, A. Isaeva, F. Reinert, Surface states and Rashba-type spin polarization in antiferromagnetic MnBi_2Te_4 (0001). *Phys. Rev. B* **100**, 121104 (2019).
41. J. H. Van Vleck, Note on the Interactions between the Spins of Magnetic Ions or Nuclei in Metals. *Rev. Mod. Phys.* **34**, 681–686 (1962).
42. B. Simons, A. Altland, *Condensed Matter Field Theory* (Cambridge Univ. Press, ed. 3, 2010).
43. P. Coleman, *Introduction to Many-Body Physics* (Cambridge Univ. Press, 2015).
44. J. Kondo, Resistance minimum in dilute magnetic alloys. *Prog. Theor. Phys.* **32**, 37–49 (1964).
45. P. Coleman, Heavy fermions and the Kondo lattice: A 21st century perspective. *arXiv:1509.05769* (2015).
46. P. W. Anderson, A poor man's derivation of scaling laws for the Kondo problem. *J. Phys. C: Solid State Phys.* **3**, 2436 (1970).
47. K. Sato, L. Bergqvist, J. Kudrnovský, P. H. Dederichs, O. Eriksson, I. Turek, B. Sanyal, G. Bouzerar, H. Katayama-Yoshida, V. A. Dinh, T. Fukushima, H. Kizaki, R. Zeller, First-principles theory of dilute magnetic semiconductors. *Rev. Mod. Phys.* **82**, 1633–1690 (2010).
48. Z. Fei, B. Huang, P. Malinowski, W. Wang, T. Song, J. Sanchez, W. Yao, D. Xiao, X. Zhu, A. F. May, W. Wu, D. H. Cobden, J. H. Chu, X. Xu, Two-dimensional itinerant ferromagnetism in atomically thin Fe_3GeTe_2 . *Nat. Mater.* **17**, 778–782 (2018).
49. M. Khela, M. Dąbrowski, S. Khan, P. S. Keatley, I. Verzhbitskiy, G. Eda, R. J. Hicken, H. Kurebayashi, E. J. G. Santos, Laser-induced topological spin switching in a 2D van der Waals magnet. *Nat. Comm.* **14**, 1378 (2023).
50. K. Yamagami, Y. Fujisawa, B. Driesen, C. H. Hsu, K. Kawaguchi, H. Tanaka, T. Kondo, Y. Zhang, H. Wadati, K. Araki, T. Takeda, Y. Takeda, T. Muro, F. C. Chuang, Y. Niimi, K. Kuroda, M. Kobayashi, Y. Okada, Itinerant ferromagnetism mediated by giant spin polarization of the metallic ligand band in the van der Waals magnet Fe_3GeTe_2 . *Phys. Rev. B* **103**, L060403 (2021).
51. M. Strungaru, M. Augustin, E. J. G. Santos, Ultrafast laser-driven topological spin textures on a 2D magnet. *NPJ Comput. Mater.* **8**, 169 (2022).
52. K. Møland, H. I. Røst, J. W. Wells, A. Sudbø, Electron-magnon coupling and quasiparticle lifetimes on the surface of a topological insulator. *Phys. Rev. B* **104**, 125125 (2021).
53. S. K. Hoffmann, W. Hilczner, J. Goslar, Weak long-distance superexchange interaction and its temperature variations in copper(II) compounds studied by single crystal EPR. *Appl. Magn. Reson.* **7**, 289–321 (1994).
54. B. Koopmans, G. Malinowski, F. Dalla Longa, D. Steiauf, M. Fähnle, T. Roth, M. Cinchetti, M. Aeschlimann, Explaining the paradoxical diversity of ultrafast laser-induced demagnetization. *Nat. Mat.* **9**, 259–265 (2010).
55. J.-Q. Yan, B. Y. Han, D. S. Parker, Y. Wu, A. A. Aczel, M. Matsuda, M. A. McGuire, B. C. Sales, A-type antiferromagnetic order in MnBi_4Te_7 and $\text{MnBi}_6\text{Te}_{10}$ single crystals. *Phys. Rev. Mat.* **4**, 054202 (2020).
56. J. Sitnicka, K. Park, P. Skupiński, K. Graszka, A. Reszka, K. Sobczak, J. Borysiuk, Z. Adamus, M. Tokarczyk, A. Avdonin, I. Fedorchenko, I. Abaloszewa, S. Turczyniak-Surdacka, N. Olszowska, J. Kołodziej, B. J. Kowalski, H. Deng, M. Konczykowski, L. Krusin-Elbaum, A. Wołoś, Systemic consequences of disorder in magnetically self-organized topological $\text{MnBi}_2\text{Te}_4/(\text{Bi}_2\text{Te}_3)_n$ superlattices. *2D Mater.* **9**, 015026 (2022).
57. H. Tan, B. Yan, Distinct magnetic gaps between antiferromagnetic and ferromagnetic orders driven by surface defects in the topological magnet MnBi_2Te_4 . *Phys. Rev. Lett.* **130**, 126702 (2023).
58. R. Mei, Y.-F. Zhao, C. Wang, Y. Ren, D. Xiao, C.-Z. Chang, C.-X. Liu, Electrically controlled anomalous hall effect and orbital magnetization in topological magnet MnBi_2Te_4 . *Phys. Rev. Lett.* **132**, 066604 (2024).
59. M. Bernardi, C. Ataca, M. Palumbo, J. C. Grossman, Optical and electronic properties of two-dimensional layered materials. *Nanophotonics* **6**, 479–493 (2017).
60. E. Carpena, E. Mancini, C. Dallera, M. Brenna, E. Puppini, S. de Silvestri, Dynamics of electron-magnon interaction and ultrafast demagnetization in thin iron films. *Phys. Rev. B* **78**, 174422 (2008).
61. A. L. Chekhov, Y. Behovits, J. J. F. Heitz, C. Denker, D. A. Reiss, M. Wolf, M. Weinelt, P. W. Brouwer, M. Münzenberg, T. Kampfrath, Ultrafast demagnetization of iron induced by optical versus terahertz pulses. *Phys. Rev. X* **11**, 041055 (2021).
62. A. Eschenlohr, M. Battiatto, P. Maldonado, N. Pontius, T. Kachel, K. Holldack, R. Mitzner, A. Föhlisch, P. M. Oppeneer, C. Stamm, Ultrafast spin transport as key to femtosecond demagnetization. *Nat. Mater.* **12**, 332–336 (2013).
63. L. Guidoni, E. Beaupaire, J.-Y. Bigot, Magneto-optics in the ultrafast regime: Thermalization of spin populations in ferromagnetic films. *Phys. Rev. Lett.* **89**, 017401 (2002).
64. A. V. Kime, R. V. Pisarev, J. Hohlfield, T. Rasing, Ultrafast quenching of the antiferromagnetic order in FeBO_3 : Direct optical probing of the phonon-magnon coupling. *Phys. Rev. Lett.* **89**, 287401 (2002).
65. T. Kise, T. Ogasawara, M. Ashida, Y. Tomioka, Y. Tokura, M. Kuwata-Gonokami, Ultrafast spin dynamics and critical behavior in half-metallic ferromagnet: $\text{Sr}_2\text{FeMoO}_6$. *Phys. Rev. Lett.* **85**, 1986–1989 (2000).
66. K. Mishra, R. M. Rowan-Robinson, A. Ciuculkaite, C. S. Davies, A. Dmitriev, V. Kapaklis, A. V. Kime, A. Kirilyuk, Ultrafast demagnetization control in magnetophotonic surface crystals. *Nano Lett.* **22**, 9773–9780 (2022).
67. C. D. Stanciu, A. Tsukamoto, A. V. Kime, F. Hansteen, A. Kirilyuk, A. Itoh, T. Rasing, Subpicosecond magnetization reversal across ferrimagnetic compensation points. *Phys. Rev. Lett.* **97**, 217204 (2007).
68. R. Takahashi, Y. Tani, H. Abe, M. Yamasaki, I. Suzuki, D. Kan, Y. Shimakawa, H. Wadati, Ultrafast demagnetization in NiCo_2O_4 thin films probed by time-resolved microscopy. *Appl. Phys. Lett.* **119**, 102404 (2021).
69. P. Tengdin, W. You, C. Chen, X. Shi, D. Zusin, Y. Zhang, C. Gentry, A. Blonsky, M. Keller, P. M. Oppeneer, H. C. Kapteyn, Z. Tao, M. M. Murnane, Critical behavior within 20 fs drives the out-of-equilibrium laser-induced magnetic phase transition in nickel. *Sci. Adv.* **4**, eaap9744 (2018).

70. J. Wang, C. Sun, J. Kono, A. Oiwa, H. Munekata, Ł. Cywiński, L. J. Sham, Ultrafast quenching of ferromagnetism in InMnAs induced by intense laser irradiation. *Phys. Rev. Lett.* **95**, 167401 (2005).
71. M. Wietstruk, A. Melnikov, C. Stamm, T. Kachel, N. Pontius, M. Sultan, C. Gahl, M. Weinelt, H. A. Dürr, U. Bovensiepen, Hot-electron-driven enhancement of spin-lattice coupling in Gd and Tb 4f ferromagnets observed by femtosecond X-ray magnetic circular dichroism. *Phys. Rev. Lett.* **106**, 127401 (2011).
72. J.-X. Qiu, C. Tzschaschel, J. Ahn, A. Gao, H. Li, X. Y. Zhang, B. Ghosh, C. Hu, Y. X. Wang, Y. F. Liu, D. Bérubé, T. Dinh, Z. Gong, S. W. Lien, S. C. Ho, B. Singh, K. Watanabe, T. Taniguchi, D. C. Bell, H. Z. Lu, A. Bansil, H. Lin, T. R. Chang, B. B. Zhou, Q. Ma, A. Vishwanath, N. Ni, S. Y. Xu, Axion optical induction of antiferromagnetic order. *Nat. Mater.* **22**, 583–590 (2023).
73. K. Yasuda, M. Mogi, R. Yoshimi, A. Tsukazaki, K. S. Takahashi, M. Kawasaki, F. Kagawa, Y. Tokura, Quantized chiral edge conduction on domain walls of a magnetic topological insulator. *Science* **358**, 1311–1314 (2017).
74. O. Breunig, Y. Ando, Opportunities in topological insulator devices. *Nat. Rev. Phys.* **4**, 184–193 (2022).
75. S. H. Lee, D. Graf, L. Min, Y. Zhu, H. Yi, S. Ciocys, Y. Wang, E. S. Choi, R. Basnet, A. Fereidouni, A. Wegner, Y. F. Zhao, K. Verlinde, J. He, R. Redwing, V. Gopalan, H. O. H. Churchill, A. Lanzara, N. Samarth, C. Z. Chang, J. Hu, Z. Q. Mao, Evidence for a magnetic-field-induced ideal type-II Weyl state in antiferromagnetic topological insulator Mn(Bi_{1-x}Sb_x)₂Te₄. *Phys. Rev. X* **11**, 031032 (2021).
76. C. Yan, E. Green, R. Fukumori, N. Protic, S. H. Lee, S. Fernandez-Mulligan, R. Raja, R. Erdakos, Z. Mao, S. Yang, An integrated quantum material testbed with multi-resolution photoemission spectroscopy. *Rev. Sci. Instrum.* **92**, 113907 (2021).
77. S. Harris, *An Introduction to the Theory of the Boltzmann Equation (Dover Books on Physics)* (Dover Publications, 2004).
78. G. Grimvall, *The Electron-Phonon Interaction in Metals*, Series of Monographs on Selected Topics in Solid State Physics (North-Holland Publishing Co., 1981).
79. P. B. Allen, Theory of thermal relaxation of electrons in metals. *Phys. Rev. Lett.* **59**, 1460–1463 (1987).
80. J. Ning, Y. Zhu, J. Kidd, Y. Guan, Y. Wang, Z. Mao, J. Sun, Subtle metastability of the layered magnetic topological insulator MnBi₂Te₄ from weak interactions. *NPJ Comput. Mater.* **6**, 157 (2020).
81. B. Li, J. Q. Yan, D. M. Pajerowski, E. Gordon, A. M. Nedić, Y. Szyuk, L. Ke, P. P. Orth, D. Vaknin, R. J. McQueeney, Competing magnetic interactions in the antiferromagnetic topological insulator MnBi₂Te₄. *Phys. Rev. Lett.* **124**, 167204 (2020).
82. J. A. Sobota, S. Yang, J. G. Analytis, Y. L. Chen, I. R. Fisher, P. S. Kirchmann, Z. X. Shen, Ultrafast optical excitation of a persistent surface-state population in the topological insulator Bi₂Se₃. *Phys. Rev. Lett.* **108**, 117403 (2012).
83. S. Blundell, *Magnetism in Condensed Matter*, Oxford Master Series in Condensed Matter Physics (Oxford Univ. Press, 2014).
84. Z. A. Jahangirli, E. H. Alizade, Z. S. Aliev, M. M. Otrokov, N. A. Ismayilova, S. N. Mammadov, I. R. Amiraslanov, N. T. Mamedov, G. S. Orudjev, M. B. Babanly, A. M. Shikin, E. V. Chulkov, Electronic structure and dielectric function of Mn-Bi-Te layered compounds. *J. Vac. Sci. Technol. B Nanotechnol. Microelectron.* **37**, 062910 (2019).
85. M. P. Seah, W. A. Dench, Quantitative electron spectroscopy of surfaces: A standard data base for electron inelastic mean free paths in solids. *Surf. Interface Anal.* **1**, 2–11 (1979).

Acknowledgments: We thank J. Ning from Tulane University for providing details of the published data on the heat capacity calculation. We also thank Y. Bai, J. Park, and P. Littlewood at the University of Chicago, as well as H. Pfau and C. Chang at Pennsylvania State University for helpful discussions. **Funding:** This work was supported by the US Department of Energy, DE-SC0022960 (K.D.N., W.L., G.B., C.Y., C.I.J.J., H.L., Q.G., and S.Y.) and DE-SC0022983 (J.D., T.W., and X.-X.Z.), and by the National Science Foundation through the Penn State 2D Crystal Consortium-Materials Innovation Platform 2DCC-MIP under NSF Cooperative Agreement DMR 2039351 (S.H.L. and Z.M.). **Author contributions:** Conceptualization and supervision: S.Y. μ ARPES and trARPES measurements: K.D.N., W.L., G.B., C.Y., C.I.J.J., H.L., Q.G., and S.Y. MBE growth: K.D.N. and W.L. trMOKE experiments: J.D., T.W., and X.-X.Z. Single-crystal growth: S.H.L. and Z.M. Theoretical support: C.L. and B.Y. Data analysis and theoretical calculations: K.D.N. Writing—original draft: K.D.N. and S.Y. Writing—review and editing: K.D.N., S.Y., X.-X.Z., C.L., Z.M., G.B., S.H.L., J.D., and B.Y. **Competing interests:** The authors declare that they have no competing interests. **Data and materials availability:** All data needed to evaluate the conclusions in the paper are present in the paper and/or the Supplementary Materials.

Submitted 1 January 2024

Accepted 2 July 2024

Published 9 August 2024

10.1126/sciadv.adn5696