


# EES Catalysis

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: L. Pile, G. Jones, A. Nambo, M. L. Carreon, M. Benamara and F. Gorky, *EES Catal.*, 2025, DOI: 10.1039/D5EY00069F.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

# Leveraging Oxygen Mobility with Zirconia in Low-Temperature Plasma for Enhanced Methane Reforming to Syngas

FNU Gorky,<sup>a</sup> Levi Pile,<sup>a</sup> Grace Jones,<sup>a</sup> Apolo Nambo,<sup>b</sup> Mourad Benamara,<sup>c</sup> and Maria L. Carreon<sup>a,†</sup>

<sup>a</sup>Ralph E. Martin Department of Chemical Engineering, University of Arkansas, 3202 Bell Engineering Center Fayetteville, AR 72701-1201, USA.

<sup>b</sup>Bert Thin Films, LLC, 625 Myrtle St, Louisville, KY 40298, USA.

<sup>c</sup>Materials Science and Engineering Program, Institute for Nanoscience and Engineering, University of Arkansas, Fayetteville, AR, 72701 USA

<sup>†</sup>Corresponding author e-mail address: mc138@uark.edu (Maria L. Carreon).

## Broader Context Statement

Global energy demands and the urgent need to combat climate change call for innovative approaches that convert raw materials into cleaner fuels. In this context, dry methane reforming (DRM) emerges as a promising route to valorize methane and carbon dioxide, transforming greenhouse gases into syngas. Our research aims to understand the oxygen mobility of zirconia within a low-temperature, electron-mediated plasma environment to unravel mechanistic insights that address two challenges: enhancing syngas yields at room temperature and mitigating catalyst deactivation from carbon deposition. Comprehensive gas phase and surface analysis revealed zirconia's ability to shuttle oxygen between its lattice and surface sustains dynamic redox cycles, encouraging plasma driven activation pathways for methane and CO<sub>2</sub> and simultaneously gasifying nascent carbon deposits to prevent coking. Compared with the conventional route DRM, our plasma catalytic system achieves significant reductions in energy input, and prolonged catalyst stability. These findings inform the rational design of oxygen mobility focused materials, paving the way for scalable, decentralized syngas production and next-gen electrified energy conversion technologies.



## ARTICLE

View Article Online

DOI: 10.1039/DSEY00069F

# Leveraging Oxygen Mobility with Zirconia in Low-Temperature Plasma for Enhanced Methane Reforming to Syngas

Received 00th January 20xx,  
Accepted 00th January 20xx


DOI: 10.1039/x0xx00000x

FNU Gorky,<sup>a</sup> Levi Pile,<sup>a</sup> Grace Jones,<sup>a</sup> Apolo Nambo,<sup>b</sup> Mourad Benamara,<sup>c</sup> and Maria L. Carreon<sup>a,†</sup>

Despite extensive efforts to optimize the single-step production of syngas, hydrocarbons, and oxygenates via plasma catalysis, several challenges remain unresolved. In particular, understanding the various reaction pathways is hindered by the complexity of the reactions and the diverse range of chemical products formed. In this study, our main objective is to evaluate and compare the influence of zirconia on reaction pathways, methane ( $\text{CH}_4$ ) and carbon dioxide ( $\text{CO}_2$ ) conversions (%), and syngas selectivity (%) relative to the plasma-only route. Experiments were conducted at low Radio-frequency plasma power of 50 Watts without external heating. The results demonstrated significantly enhanced conversions of carbon dioxide and methane when the reaction chamber was packed with zirconia ( $\text{ZrO}_2$ ). Methane conversion was observed highest at rich  $\text{CO}_2$  feed [ $\text{CO}_2:\text{CH}_4$  (2:1)], while plasma only revealed conversion of 20.1 %. After packing zirconia the conversion led to 71.2% (3.5 times increment). On the other hand, carbon dioxide conversions were also observed highest at feed composition of  $\text{CO}_2:\text{CH}_4$  (2:1), with plasma only (13.6%) vs. zirconia packed (60.9%) revealing a 4.4 times increase. Interestingly, at the rich  $\text{CO}_2$  feed composition, the syngas product ( $\text{CO} + \text{H}_2$ ) selectivity increased after packing  $\text{ZrO}_2$  by 1.1 times for  $\text{CO}$  and 1.2 times for  $\text{H}_2$ . Optical emission spectroscopy (OES) analysis revealed important insights on gas phase, with signatures of atomic oxygen ( $\text{O}$ ) being the dominant plasma species in the gas phase under plasma-only conditions, while their intensities plummeted when zirconia was introduced, indicating active oxygen diffusion onto the surface of zirconia. Raman spectroscopy and X-ray photoelectron spectroscopy (XPS) confirmed important surface alterations after plasma exposure and most importantly provided experimental proof on zirconia's oxygen mobility. These findings provided an integral perspective into the design of catalytic materials that enhance oxygen mobility, enabling low-temperature and energy-efficient dry methane reforming for a sustainable future.

## Introduction

The dry reforming of methane (DRM) is a chemical reaction in which methane ( $\text{CH}_4$ ) and carbon dioxide ( $\text{CO}_2$ ) react to form synthetic gas (syngas), a mixture of hydrogen ( $\text{H}_2$ ) and carbon monoxide ( $\text{CO}$ ). DRM is a well-studied and highly endothermic reaction (see Eq 1) and requires high temperatures (800–1000 °C) and moderate (1–10 bar) to high (20–30 bar) pressures.<sup>1</sup>



The interest in DRM has grown to utilize  $\text{CO}_2$  to obtain value-added products and to make use of high  $\text{CO}_2$  content natural gas deposits that cannot be economically used for steam reforming.<sup>1,2</sup>

Traditionally, hydrocarbons and oxygenate production has relied on multi-step thermal catalytic processes involving decomposition of  $\text{CH}_4$  and  $\text{CO}_2$  at elevated temperatures (800–1,000 °C) and pressures (20–50 bar) towards production of synthetic gas. To further produce essential chemicals, the produced syngas is further processed through another step via the Fischer-Tropsch synthesis

(temperatures of (250–350°C) and pressures of (20–50 bar) to produce hydrocarbons and oxygenates, such as alkanes, aldehydes, ketones, and alcohols. While effective, these steps are energy-intensive and economically demanding, driving researchers to explore alternative catalytic routes that reduce energy consumption. The growing urgency to mitigate greenhouse gas emissions while producing value-added chemicals has increased the interest on various catalytic routes such as plasma-catalytic DRM.<sup>3,4</sup>

The activation of methane and carbon dioxide poses a significant challenge in thermal catalytic processes due to their high bond dissociation energies 434.2 kJ/mol for C–H in  $\text{CH}_4$  and 530.7 kJ/mol for C=O in  $\text{CO}_2$ . These conditions necessitate extreme temperatures, which often lead to the decomposition of intermediates, limiting single pass conversions and selectivity. The look for energy alternatives positions non-thermal plasma (NTP) as a promising alternative, enabling efficient activation of  $\text{CH}_4$  and  $\text{CO}_2$  under mild conditions (room temperature and atmospheric pressure). By generating high-energy electrons in a low-temperature environment, NTP offers a non-selective but energy-efficient alternative to produce syngas,<sup>5–7</sup> hydrocarbons<sup>8–10</sup> and oxygenates<sup>11–13</sup> in a single step.

Specifically for partial oxidation of methane (POM), studies have shown that oxygen can effectively activate methane in plasma environments; however, excessive oxidation frequently results in the overproduction of  $\text{CO}_2$  and undesired byproducts.<sup>14</sup> Using  $\text{CO}_2$  as a milder oxidant offers dual benefits: mitigating two of the most prevalent greenhouse gases while producing valuable chemicals. For the specific case of plasma-

<sup>a</sup> Ralph E. Martin Department of Chemical Engineering, University of Arkansas, 3202 Bell Engineering Center, Fayetteville, Arkansas 72701-1201, United States.

<sup>b</sup> Bert Thin Films, LLC, 625 Myrtle St, Louisville, KY 40298, USA.

<sup>c</sup> Materials Science and Engineering Program, Institute for Nanoscience and Engineering, University of Arkansas, Fayetteville, AR, 72701 USA

† Corresponding author: Maria L. Carreon; Email: mc138@uark.edu

Supplementary Information available: [details of any supplementary information available should be included here]. See DOI: 10.1039/x0xx00000x



## ARTICLE

catalyst the resulting synergy enables partial oxidation pathways that favor the formation of oxygenates and hydrocarbons as products, presenting an alternative at mild conditions for DRM.<sup>15-17</sup>

Catalyst design and plasma-catalyst synergy is critical to advancing plasma-catalytic processes. While precious metals have traditionally dominated catalytic applications due to their superior performance, their high cost and limited availability make them economically unfeasible for large-scale implementation.<sup>18</sup> Research has increasingly focused on earth-abundant materials, such as silica, alumina, and zirconia, which offer comparable catalytic performance under specific conditions. However, findings from thermal catalysis do not always translate seamlessly into plasma catalysis, needing a deeper understanding of material behavior under plasma conditions.

In thermal catalytic literature, high temperatures (800-850°C) are required to operate for achieving higher efficiencies of CH<sub>4</sub> and CO<sub>2</sub> conversions. Supports like silica,<sup>19</sup> alumina,<sup>20</sup> and zirconia,<sup>21</sup> are commonly used impregnated with transition metals as catalysts. Zirconia is highly stable, over higher temperatures making it suitable for sustaining multiple cycles.<sup>22</sup> Literature, at the relatively low temperature of 600°C, show that Ni-Zr on MCM-41 achieved 91% methane conversion,<sup>23</sup> highlighting the effectiveness of zirconia-based supports even at moderate conditions. Similarly, Pt-impregnated ZrO<sub>2</sub> at 700°C exhibited 80.1% methane and 84.6% CO<sub>2</sub> conversion,<sup>24</sup> surpassing Ni-based catalysts at the same temperature. The introduction of Ni with a Zr promoter at 700°C improved the conversion to 73% methane and 76.7% for CO<sub>2</sub>,<sup>25</sup> displaying the role of metal promoters in enhancing catalytic activity. Overall, zirconia-based catalysts with Pt and Ni-Zr combinations demonstrated higher conversion at lower temperatures with less metal loading, making them more efficient for high-temperature thermal catalysis.

In plasma-catalytic systems, zirconia-based materials displayed promising performances. Particularly, Zirconia and Ceria based oxides like Ni-Ce<sub>x</sub>Zr<sub>1-x</sub>O<sub>2</sub> within a dielectric barrier discharge (DBD) plasma reactor enable CO<sub>2</sub> conversions up to 80% with 100% methane selectivity at temperatures as low as 90 °C, whereas in thermal catalysis required temperatures above 300 °C to achieve comparable results.<sup>26</sup> Plasma activation of CO<sub>2</sub> resulted in the formation of CO\* and O\* species, facilitating enhanced conversion rates at lower temperatures.<sup>27-29</sup> Furthermore, hydrogen plasma treatment of Ni-based ceria-zirconia catalysts was found to be an effective alternative to conventional thermal reduction, maintaining similar catalytic activity and strengthening Ni-support interactions.<sup>30</sup> The role of Ce and Zr promoters in hydrotalcite-derived catalysts was also examined, displaying that while Zr-containing catalysts exhibited higher activity under plasma conditions, the overall impact of these promoters on catalytic performance remained minimal.<sup>31</sup> In plasma catalysis literature, zirconia based materials have been employed for CO<sub>2</sub> hydrogenation, however, while designing the materials, the impregnation of multiple metals and ceramics makes challenging to isolate the individual contributions. In this study, we employed pristine zirconia to investigate the effect of oxygen mobility and its effect towards product distribution during dry methane reforming. Zirconia stands out as an ideal candidate for plasma-

catalytic DMR due to its intrinsic oxygen mobility, structural stability under harsh conditions, and potential to mitigate coke formation.<sup>32</sup> Coking, a persistent challenge in methane reforming, significantly degrades catalyst performance by blocking active surface with carbon build-up.<sup>21</sup> The oxygen mobility in zirconia's matrix facilitates the active removal of amorphous carbon species, preventing their buildup and prolonging catalyst life. Furthermore, the porous structure of zirconia offers the possibility to enhance its interaction with plasma, improving methane decomposition towards value added products.

Our group has previously explored NTP (RF and DBD) applications for various chemistries including ammonia synthesis,<sup>32-38</sup> dry methane reforming,<sup>13</sup> plastics decomposition to fuels,<sup>39, 40</sup> methane upgrading,<sup>8</sup> graphene synthesis from biomass,<sup>41</sup> greenhouse gas plasma based membrane separation,<sup>42</sup> carbon capture and plasma based desorption,<sup>43</sup> using various catalysts such as inorganic metal oxides,<sup>35, 38, 44, 45</sup> low-melting point alloys,<sup>46, 47</sup> perovskites,<sup>34, 39</sup> zeolites,<sup>8, 32, 43, 48</sup> hybrid materials such as MOFs,<sup>13, 36, 49</sup> porous organic materials such as CC3<sup>50</sup> for storage and catalytic applications showing the importance of tailoring materials for plasma.

Although the industry typically produces syngas via coal gasification<sup>51</sup> and steam reforming of methane,<sup>52</sup> dry methane reforming (DMR) has attracted significant research interest over the past several decades because it incorporates carbon dioxide, a major pollutant into useful products; however, the DRM reaction has faced major challenges, such as catalyst deactivation due to coking at high temperatures. Building on the extensive literature covering both thermal and plasma catalytic DRM, our study involves lowering down the amount of energy required to activate reactants, with the objective of enhancing syngas production, while employing commercial materials like zirconia. Building on extensive studies of both thermal and plasma-catalytic dry reforming of methane, we aimed to minimize the energy needed to activate CH<sub>4</sub> and CO<sub>2</sub> under low-temperature plasma. To achieve this, we selected commercial zirconia for its exceptional suitability to plasma environments because it combines outstanding thermal stability, chemical inertness to corrosive species, resistance to sintering and phase changes, and high mechanical hardness, all helps it sustain the energetic particle collisions during plasma discharges. Materials like zirconia, known for its oxygen vacancy, provides a reactive surface that can interact with plasma activated species (CO<sub>2</sub>\*, O\*) in a manner conceptually similar to that described in the recent plasma catalytic chemical looping system<sup>53</sup> involving Ce<sub>0.7</sub>Zr<sub>0.3</sub>O<sub>2</sub>.<sup>54</sup> In addition, zirconia's abundant oxygen vacancies facilitate rapid ion mobility, enabling it to capture and gasify nascent carbon deposits and thus suppress coking. Through this work, we are exploring key reaction pathways in plasma catalytic DRM and demonstrating an energy efficient approach. The overarching goal of our findings is to lay the groundwork for the future development of tailored zirconia-based thin films or membranes, offering a scalable, economically viable route, for converting greenhouse gases into valuable chemicals for sustainable energy conversion.

## Experimental

### Materials and Methods

Commercial zirconia was provided from Luxfer MEL Technologies (Manchester, England), reference number (XZO1501/09). Fumed silica were purchased from Fasco (CAB-O-SIL® M-5)



## Zirconia Characterization

The commercial zirconia catalysts used in this study were degassed under vacuum at 100 °C for 5 hours. Nitrogen physisorption isotherms were measured at 77 K using a 3Flex Micrometrics instrument to determine the Brunauer–Emmett–Teller (BET) surface area, pore size, pore volume, and particle size (μm) of both fresh and plasma-exposed catalysts. The morphology of the commercial zirconia was examined using an FEI Nova Nanolab 200 Dual-Beam system, which is equipped with a high-resolution field-emission gun analytical scanning electron microscope (SEM) operating at 15 kV. The commercial zirconia was analysed using powder X-ray diffraction (XRD) with a Panalytical X'Pert Materials Research Diffractometer, employing Cu K $\alpha$  radiation ( $\lambda = 1.54 \text{ \AA}$ ) over a 2 $\theta$  range of 20°–80°. To ensure accurate crystallinity assessment, the intensity scale (au) was standardized across all catalysts. X-ray photoelectron spectroscopy (XPS) was carried out on a VersaProbe II system featuring a monochromatic Al K $\alpha$  source. All XPS measurements were acquired with the electron take-off angle set at 47°. Raman spectra were recorded on a Horiba LabRAM HR micro-Raman spectrometer (Horiba Scientific) equipped with a monochromated 532 nm laser.

## DMR Plasma Setup

The experiments were conducted in an in-house built RF plasma reactor using CO<sub>2</sub> (Airgas, 99.99%) and CH<sub>4</sub> (UHP Airgas) as reactants. The flow rates varied between 10 and 100 sccm, controlled via a mass flow controller (MFC). Plasma generation was achieved using an RF power supply with a Seren IPS, Inc. Matching Network. The reaction conditions included a plasma power range of 50–300 W and a pressure of 0.3 Torr, consistent across all experiments. Vacuum was maintained using an Edwards Dry scroll pump (nXDS6i). Each reaction used 1.2 g of zirconia, ensuring uniform catalyst loading across the electrode area. The vacuum pump's outlet was connected via copper tubing to the inlet valve of a gas chromatography (Agilent 8860) system equipped with an Agilent HP-PLOT U column 30 m × 0.320 mm × 10 μm, (see Figure S1 for complete schematic). All experiments were performed in triplicates. Key plasma species were analysed using optical emission spectroscopy (OES). Light emitted from the plasma discharge was directed through an optical system, and the emission spectra of the glow region were recorded. A dual-channel ultraviolet-visible–near-infrared (UV–vis–NIR) spectrophotometer (Avantes Inc., USB2000 Series) was used in scope mode, covering a spectral range of 200–1100 nm with a 600 lines/mm grating and a resolution of 0.4 nm. A bifurcated 400-μm fiber optic cable was employed for spectral collection. Based on optimal spectroscopy conditions, the integration time was set to 5 s with 100 averages, following the methodology established in previous studies.<sup>39</sup>

## Zirconia textural properties

Our primary investigation was dedicated towards analysing the difference on textural properties of zirconia at different calcination temperatures before conducting plasma-based reactions. The XRD revealed the effect of calcination temperature on the phases of zirconia. At 400°C, the sample predominantly exhibits cubic phases,

specifically the (111) reflection. As the temperature increases to 500°C, both cubic (111) and monoclinic (-111) phases become comparable in intensity, indicating a phase transition. At 600°C, the monoclinic phase (-111) becomes dominant Figure 1a. confirms the evidence on monoclinic phase.

We conducted the calcination at 1000°C, the sample exclusively shows monoclinic phases (-111), with no cubic phase contribution (see Figure S2). This temperature-dependent phase evolution highlighted the critical role of calcination temperature in selecting the desired zirconia phase, with cubic phases being the target for further study due its symmetric configuration. Cubic phases offer high surface area as evident via physio-chemical properties described in the experimental table (see Table 1), apart from surface area, it is well reported in literature for materials like zirconia and ceria that the cubic phases offer enhanced anionic mobility,<sup>55</sup> redox properties,<sup>56</sup> and cubic phase also offers lower elastic modulus and higher malleability over other phases such as monoclinic and tetragonal.<sup>57</sup> Based on the literature, the vacancies (defects) can be co-related with lattice relaxation observed in doped cubic zirconia. This directly implies that lower elastic modulus causes a higher degree of relaxation allowing lower binding energies with oxygen vacancy and improved mobility.<sup>58</sup>

The zirconia samples calcined at different temperatures revealed significant changes in surface area and structural properties. At 400°C, ZrO<sub>2</sub> exhibits the highest BET surface area of 122.45 m<sup>2</sup>/g and pore volume of 0.49 cm<sup>3</sup>/g, along with the smallest particle size (48.99 nm), correlating with a cubic XRD phase. As the calcination temperature increases to 500°C, the BET surface area and pore volume decrease, while pore size and particle size grow, indicating a transition to a hybrid phase exhibiting cubic + monoclinic. At 600°C, the material exhibits the lowest surface area (49.79 m<sup>2</sup>/g) and the largest particle size (120.48 nm), dominated by the monoclinic phase (see Figure 1b. and Table 1.).

Similarly, our experimental data revealed unimodal pore size distribution. At a lower calcination temperature (400°C), the pore size was smaller (6.3 nm), whereas higher temperatures led to an increase in pore width (up to 28 nm) (see Figure S3). The N<sub>2</sub>-isotherm revealed characteristics of Type II isotherms, which were characterized by an initial monolayer adsorption at lower relative pressures, followed by a sharp rise that indicated multilayer adsorption at intermediate pressures. The presence of a hysteresis loop suggests the existence of pores, indicating that capillary condensation had occurred within the pores. This was classified as an IUPAC Type H3 loop,<sup>59</sup> where the adsorption branch resembled a Type II isotherm, and the lower limit of the desorption branch was typically located at the cavitation-induced  $p/p_0$ . Hysteresis loops of Type H3 were associated with non-rigid aggregates of plate-like particles but also appeared when the pore network consisted of macropores that were not entirely filled with pore condensate.<sup>59</sup> These results revealed the influence of calcination temperature on



## ARTICLE

## Journal Name

zirconia's phase, porosity, and surface characteristics, with lower temperatures favouring the desirable cubic phase. In literature it is


well noted that cubic zirconia facilitates redox reactions, which can further enhance oxygen mobility.<sup>60</sup>

[View Article Online](#)

DOI: 10.1039/DSEY00069F

**Table 1.** Textural properties for Zirconia at different calcination temperature

Sample	ZrO <sub>2</sub> -400	ZrO <sub>2</sub> -500	ZrO <sub>2</sub> -600
BET Surface Area (m <sup>2</sup> /g)	122.45	76.23	49.79
Langmuir Surface Area (m <sup>2</sup> /g)	163.96	104.19	67.51
Pore Volume (cm <sup>3</sup> /g)	0.49	0.46	0.39
Pore Size (nm)	14.19	22.39	29.92
Particle Size (nm)	48.99	78.70	120.48
t-Plot external surface area (m <sup>2</sup> /g)	133.82	76.60	51.30

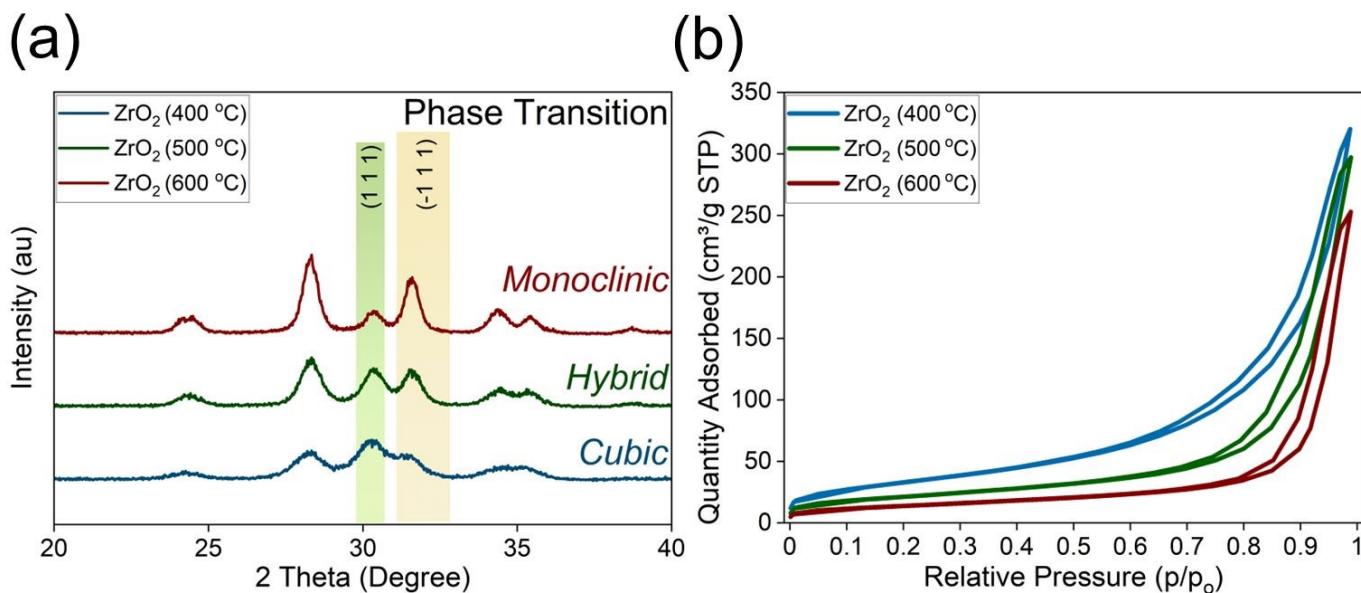

**Figure 1.** (a) XRD revealing effect of calcination temperature on ZrO<sub>2</sub> phases; (b) Nitrogen isotherms at different temperature on different zirconia calcination temperature.

## Results and discussion

### Plasma Only

Our initial investigations entailed acquiring the methane and carbon dioxide conversion *with and without external cooling*. Steady state for DRM reactions was observed after 45 minutes, with long operation time, the temperature around the electrode area increased. To differentiate the effect of heat vs. plasma, we studied how varying plasma power will effect methane and carbon dioxide conversion. This was investigated at plasma only conditions at an *in-house* RF (radiofrequency) plasma reactor under varying power conditions, with and without external cooling. A cooling fan


positioned near the electrode area to control temperature. The total flow rate was maintained at 25 sccm with a CO<sub>2</sub>:CH<sub>4</sub> feed ratio of 1:1, and no external heating applied. All results were averaged from triplicate measurements over a reaction time of 2 hours. We selected these parameters as baseline, as most of the experimental results demonstrated that increasing plasma power led to higher methane and carbon dioxide conversion in both configurations. Without the cooling fan, methane conversion increased from 15.51% at 50 W to 42.77% at 300 W, while carbon dioxide conversion rose from 11.24%



to 35.3%. A similar trend was observed with the cooling fan, where methane conversion improved from 14.83% at 50 W to 46% at 300 W, and carbon dioxide conversion increased from 10.77% to 37.53%. At all power levels, slightly higher conversions were recorded with the fan, suggesting improved reaction efficiency due to better temperature regulation near the electrodes. Additionally, standard deviations were generally lower with the external cooling, revealing more stable reaction conditions. The results highlight the significant role of plasma power in enhancing conversion efficiency and suggest that thermal management strategies, such as electrode cooling, can further optimize performance in plasma-assisted dry methane reforming. However, the comparative difference was minor and for the further studies we conducted experiments without fan to reduce energy requirements. We also selected 50 Watts (minimal plasma power) to further explore with various parameters, such as plasma power (Watts), feed ratio ( $\text{CO}_2:\text{CH}_4$ ), various flow rates (sccm) to further analyze the methane and carbon dioxide conversion in a more comprehensive way (see **Figure S4**).

The effect of total flow rate on methane and carbon dioxide conversion was investigated at the minimal plasma power of 50 W to reduce energy cost. The  $\text{CO}_2:\text{CH}_4$  feed ratio was maintained at 1:1, and no external heating was applied over a reaction time of 2 hours. The results indicated a decreasing trend in both methane and carbon dioxide conversion as the total flow rate increased. At 10 sccm, the highest methane and carbon dioxide conversions were observed at 25% and 17.20%, respectively. As the flow rate increased to 25 sccm, the conversions slightly dropped to 19.23% for methane and 15.60% for  $\text{CO}_2$ . Further increasing the flow rate to 40 sccm, 75 sccm, and 100 sccm led to a continued decline in conversions, with the lowest values recorded at 100 sccm (8.77% methane and 7.73%  $\text{CO}_2$  conversion). The experimental observations revealed that lower flow rates favored higher reactant residence time, possibly increasing the lifetime of active species allowing for more effective plasma-activated reactions on the gas phase. On the other hand, at higher flow rates the lower residence time led to limited reactant activation and increased the possibility to undergo recombination of initial plasma species in the afterglow region, eventually leading to lower conversion efficiencies. The standard deviation values remained relatively small across all conditions, indicating consistent experimental reproducibility.

Finally, the effect of  $\text{CO}_2:\text{CH}_4$  feed ratio on methane and carbon dioxide conversion was examined in the RF plasma reactor at 50 W with a total flow rate of 25 sccm. The results demonstrated that higher methane content in the feed mixture led to increased  $\text{CH}_4$  and  $\text{CO}_2$  conversions. The 3:1 ratio exhibited the highest conversions, with 26.1% for methane and 17.8% for  $\text{CO}_2$ , while a progressive decrease was observed as the  $\text{CH}_4$  ratio increased, reaching the lowest values at 1:3  $\text{CO}_2:\text{CH}_4$  (9.3% methane and 7.8%  $\text{CO}_2$  conversion). This trend suggested that excess  $\text{CO}_2$  enhances plasma reactivity, as evident from the experimental data that higher methane rich composition can lead to methane recombination which eventually leads to lower conversion of methane.

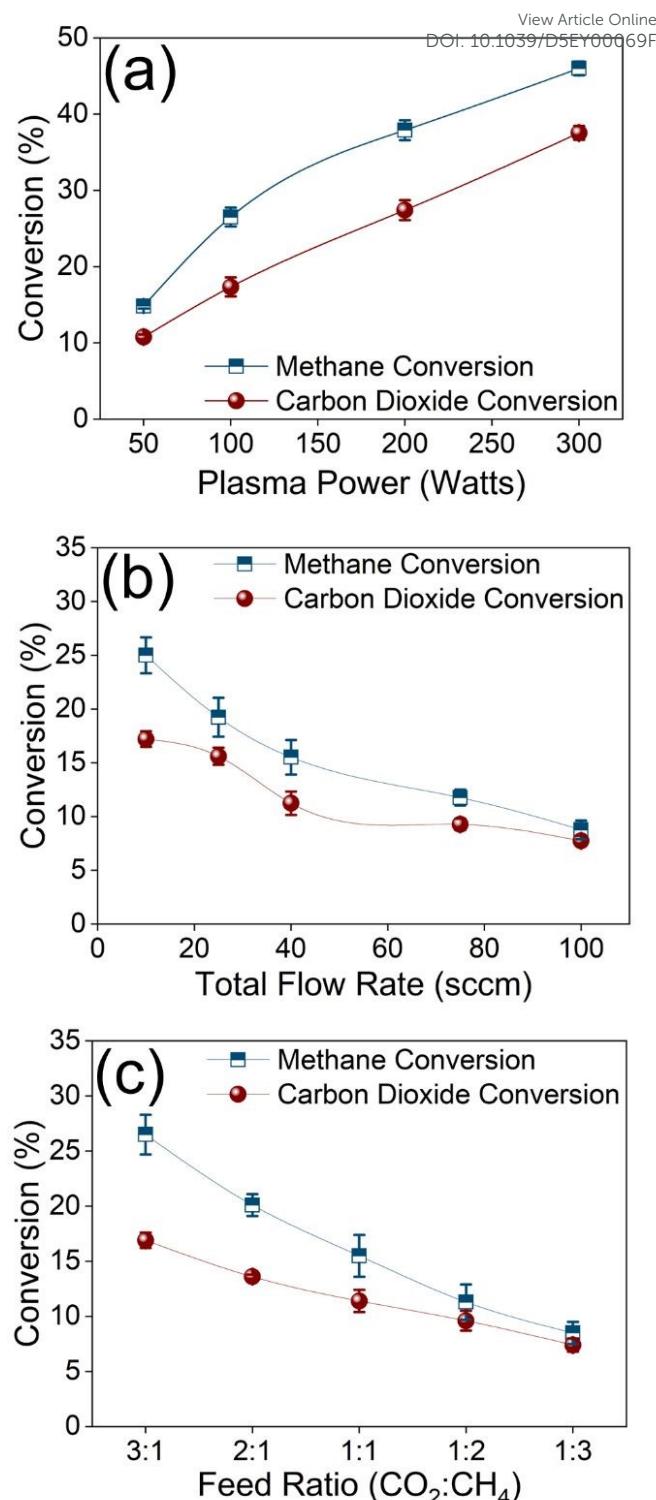

**Figure 2.** Effect of Methane and Carbon Dioxide conversion (a) Plasma power, (b) Total flow rate, (c) Feed ratio; at Plasma Power of 50 Watts, no external heating, reaction time of 2 hours.

#### Zirconia Plasma Catalysis

Our next investigations lead towards understanding the impact of packed bed reaction in plasma-DRM. The packed bed containing 1.2 grams of cubic zirconia ( $\text{ZrO}_2$ ) versus plasma only conditions on




## ARTICLE

methane and carbon dioxide conversion was evaluated in an RF plasma reactor at 50 W, with a total flow rate of 25 sccm and equimolar feed ratio. The results revealed that conversion efficiencies were widely enhanced with  $\text{ZrO}_2$  across all feed ratios. Under plasma-only conditions, the equimolar feed (1:1) yielded a methane conversion of 15.5% and a  $\text{CO}_2$  conversion of 11.97%. However, with addition of  $\text{ZrO}_2$  the equimolar system achieved a methane conversion of 63.73% and a  $\text{CO}_2$  conversion of 57.19% approximately 4.1 folds and 4.7 folds increase, respectively. In addition, under  $\text{CO}_2$ -rich conditions (2:1), methane conversion improved from 20.1% to 71.2% (a 3.5 folds increase) and  $\text{CO}_2$  conversion from 13.6% to 60.9% (a 4.4-fold increase), while under  $\text{CH}_4$  rich conditions (1:2), the values increased from 11.3% to 55.1% for methane (a 4.8 folds improvement) and from 9.8% to 41.6% for  $\text{CO}_2$  (a 4.2 folds improvement). These findings confirmed that the addition of  $\text{ZrO}_2$  had markedly boosted conversions (%) compared to plasma-only conditions (Figure 3.). The synergistic interaction between the plasma and zirconia likely played an integral role in enhancing these conversions.  $\text{ZrO}_2$ , known for its oxygen-mobilizing capabilities, facilitated oxygen diffusion, promoting efficient redox pathways for important plasma species. Herein, these results displayed the importance of plasma-material synergy, where active oxygen species generated in plasma can interact with the zirconia surface, further driving symmetrical molecules like methane to activate and dissociate. Similar observations were also identified in thermal catalytic routes with zirconia employed as in thermal catalytic routes displayed very high conversions for methane and carbon dioxide (see Table S1. for complete state of the art).

For objectivity, we compared an inert material (silica) performance with zirconia. At similar parameters previously reported, we compared analytically No catalyst (plasma only), a packed-bed with fumed silica, and a packed-bed with zirconia, across  $\text{CO}_2:\text{CH}_4$  feed ratios of 2:1, 1:1, and 1:2. In the plasma only setup, methane conversion decreased from 20.1 % at a 2:1 ratio to 15.5 % at 1:1 and 11.3 % at 1:2, while  $\text{CO}_2$  conversion fell from 13.6 % to 12.0 % and 9.9 %, respectively. Introducing a silica-packed bed boosted performance: methane conversion rose to 42.8 % at 2:1, 38.4 % at 1:1, and 35.6 % at 1:2, with corresponding  $\text{CO}_2$  conversions of 29.6 %, 23.4 %, and 18.2 %. The zirconia-packed bed delivered the highest conversions in every case, achieving 71.2 % methane and 60.9 %  $\text{CO}_2$  conversions at 2:1, then 63.7 % and 57.2 % at 1:1, and finally 55.2 % and 41.7 % at 1:2 (see Figure S5). Overall, both packed-bed reactors evidently outperformed the plasma-only setup, with zirconia proving the most effective material for methane and carbon dioxide conversions.

This enhanced conversion directly influenced product selectivity, favouring syngas ( $\text{CO}$  and  $\text{H}_2$ ) and  $\text{C}_2$  alkane and olefins, while suppressing the formation of heavier alkanes and oxygenates. The syngas production varied with changes in the feed ratio ( $\text{CO}_2:\text{CH}_4$ ). When comparing plasma-only operation to the zirconia-packed system, a notable increase in syngas production was observed after packing with zirconia (see Figure 4). The comparative syngas selectivity increased +14% after zirconia packing for  $\text{CO}_2$ -rich feed ratio (2:1  $\text{CO}_2:\text{CH}_4$ ), followed by the equimolar feed (1:1  $\text{CO}_2:\text{CH}_4$ ) with +10.9% increment in selectivity, and the methane-rich feed (1:2  $\text{CO}_2:\text{CH}_4$ ) with +8.5% increment in selectivity.

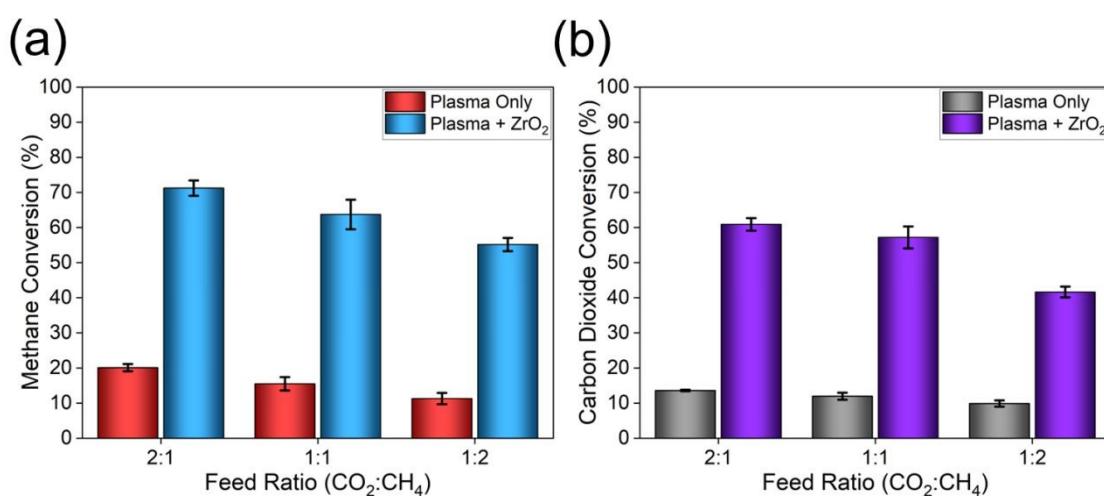

**Figure 3.** Comparing (a) Methane and (b) Carbon Dioxide conversions with Plasma only Vs. Packed bed reactor with (Zirconia) at a total flow rate: 25 sccm, at different feed ratios ( $\text{CO}_2:\text{CH}_4$ ), Plasma Power:50 Watts, reaction time: 2 hours.

Interestingly, the highest overall syngas ( $\text{H}_2+\text{CO}$ ) production in the packed bed with zirconia occurred at the  $\text{CO}_2$ -rich feed ratio (2:1  $\text{CO}_2:\text{CH}_4$ ) with 85.06% selectivity, followed by the equimolar feed (1:1  $\text{CO}_2:\text{CH}_4$ ) with 74.13% selectivity, and the methane-rich feed (1:2

$\text{CO}_2:\text{CH}_4$ ) with 60.23% selectivity. The increased interaction of the zirconia surface with oxygen species likely facilitated  $\text{CO}_2$  activation, enhancing syngas yield. Additionally, olefin ( $\text{C}_2\text{H}_4$ ) selectivity improved at methane rich feed ratio (1:2  $\text{CO}_2:\text{CH}_4$ ) with plasma only

at 14% selectivity and 11.5% with zirconia, suggesting a stronger plasma recombination of methane derived active species that leads to olefins. Conversely, alkane production was observed highest at methane rich feed ratio with ethane ( $C_2H_6$ ) selectivity for Plasma only vs. Zirconia (16.5% vs. 12.8%), while small fraction of propane ( $C_3H_8$ ) selectivity was observed slightly higher with plasma only vs. zirconia (1.5% vs. 1.4%). This decline suggests that the selectivity of the products was favoured towards syngas, rather than light hydrocarbons ( $C_2$ - $C_3$ ) (see **Figure 4**.)

Especially, in case of methane rich feed composition (1:2  $CO_2$ : $CH_4$ ) the syngas production, CO selectivity increased from 30.7% plasma-only to 35.9% (zirconia-packed bed), while  $H_2$  selectivity significantly increased from 20.8% to 24.2%. The increased availability of active oxygen species on the zirconia surface likely facilitated  $CO_2$  activation and oxygen mobility, further improving the syngas yield. Additionally, olefin ( $C_2H_4$ ) selectivity decreased from 14.4% (plasma only) to 11.5% (zirconia), displaying no enhancement on methane upgrading towards olefins over zirconia. While alkane production remained relatively higher in plasma only, observed with ethane ( $C_2H_6$ ) selectivity (16.5 % vs. 12.8%), while propane ( $C_3H_8$ ) selectivity keep constant from 1.5% to 1.4% suggested that the zirconia surface promoted single carbon-hydrogen species consumption into methane reforming towards syngas rather than their recombination to alkane formation(see **Figure 4a**). Furthermore, oxygenated compounds such as formaldehyde selectivity slightly increased (2 % vs. 3.7%), while acetone production decreased (0.6% to 0.2%). Interestingly, trace amounts of methanol (0.1%) and ethanol (0.05%) were detected only in the zirconia-packed system (**Figure 4b**), indicating improved oxygen interaction between plasma and zirconia. The trends observed with rich methane feed improved more with equimolar feed (**Figure 4c,d**) and the best selectivity was observed with  $CO_2$  rich feed 2:1 ( $CO_2$ : $CH_4$ ) (**Figure 4e,f**) with minor fraction of oxygenated compounds such as aldehydes, ketones and alcohols. Formaldehyde and acetone were observed highest with plasma only at  $CO_2$  rich feed (5% and 0.9%).


Moreover, we compared the product selectivity performances with silica packed bed, please see **Figure S6**.<sup>10,19,24,25,26,27</sup> For syngas, in the plasma-only mode, CO selectivity was 39.5 %, rising to 41.1 % over silica and to 46.5 % over zirconia. Hydrogen selectivity dropped from 23.7 % in plasma alone to 18.3 % with silica but rose to 27.6 % with zirconia. Incase of alkenes, ethylene selectivity increased from 13.1 % in the bare plasma to 15.2 % on silica before falling to 8.6 % on zirconia, while (alkanes) ethane rose moderately from 15.4 % (plasma only) to 17.2 % (silica) then fell to 11.1 % (zirconia). Propane selectivity was low in all configurations but increased gradually from 0.6 % to 1.0 % to 1.7 % across plasma, silica, and zirconia.

Furthermore, to investigate on zirconia's properties after plasma exposure, we conducted experiments with three cycles (6 hours) to check the stability at 50 Watts of RF plasma power. The results revealed no critical changes in crystallinity or phases observed, uncovering robustness for long DRM operations. (see **Figure 5**).

Similarly, no textural or morphological changes were observed for all three cycles on SEM images (see **Figure S7**), the zirconia-packed reactor exhibited only minimal declines in activity, highlighting its stability under extended operation (see **Figure S8**). At a  $CO_2$ : $CH_4$  feed ratio of 2:1, methane conversion decreased gently from 71.2 % in the first cycle to 70.1 % in the second and 68.2 % in the third, while  $CO_2$  conversion decreased from 60.9 % to 58.8 % and 58.1 %, respectively. A similar trend was seen at a 1:1 feed ratio, where methane conversion dropped from 63.7 % to 61.8 % and then to 60.3 %, and  $CO_2$  conversion dropped from 57.2 % to 55.3 % and 54.8 %. Under methane rich feed(1:2), methane conversion only edged down from 55.2 % to 53.3 % and 52.8 %, with  $CO_2$  conversion moving from 41.7 % to 40.2 % then to 39.2 %. These slight decreases on the order of 2–3 percentage points over 6 hours demonstrated that zirconia maintained high reactivity and conversion (%) with minimal deactivation over extended plasma exposure.



## ARTICLE

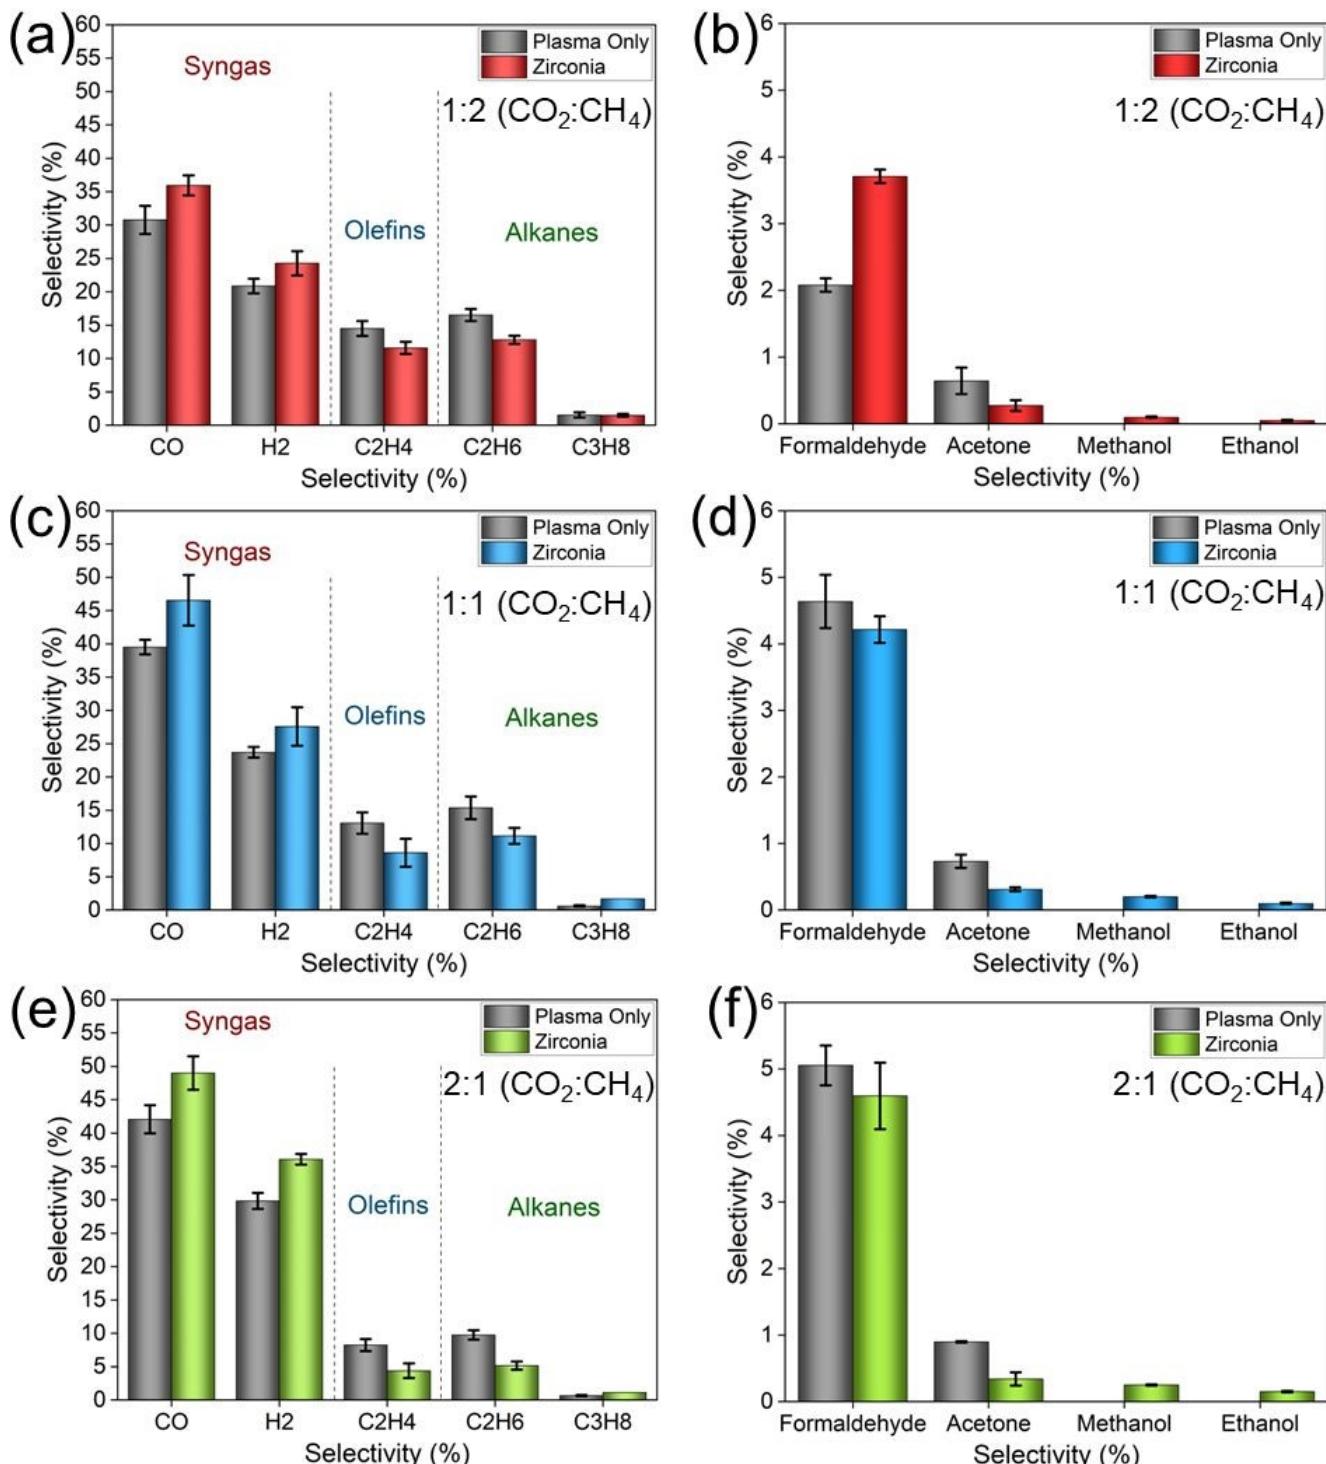


**Figure 4.** Dry methane reforming product distribution; (a) Gases product distribution (syngas, olefins, alkanes), (b) Oxygenates product distribution (aldehydes, ketones, alcohols) at rich methane feed ratio (1:2 CO<sub>2</sub>:CH<sub>4</sub>); (c) Gases product distribution, (d) Oxygenates product distribution at equimolar feed ratio (1:1 CO<sub>2</sub>:CH<sub>4</sub>); (e) Gases product distribution, (f) Oxygenates product distribution at rich carbon dioxide feed ratio (2:1 CO<sub>2</sub>:CH<sub>4</sub>); for zirconia and plasma only, at a total flow rate: 25 sccm, Feed Ratio: varied (CO<sub>2</sub>:CH<sub>4</sub>), Plasma Power: 50 Watts, Reaction Time: 2 hours.

## ARTICLE

View Article Online

DOI: 10.1039/DSEY00069F

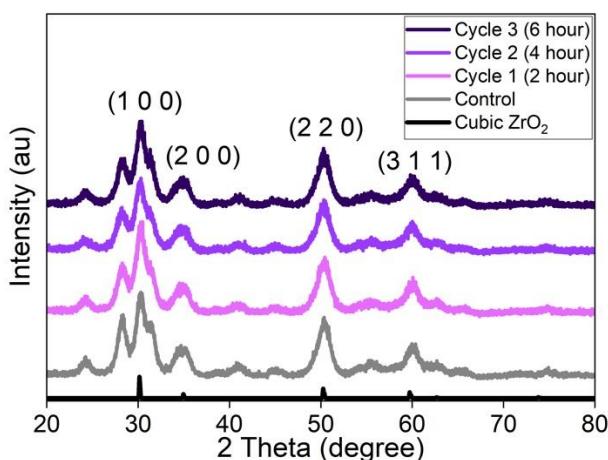

**Figure 5.** XRD revealing effect of plasma exposure with multiple cycles on  $\text{ZrO}_2$  phases, revealing longevity and stability to cubic zirconia, at a total flow rate: 25 sccm, Feed Ratio: 1:1 ( $\text{CO}_2:\text{CH}_4$ ), Plasma Power: 50 Watts, Reaction Time: 2 hours.

#### Gas Phase Analysis

We conducted detailed optical emission spectroscopy (OES) analyses for both the combined  $\text{CO}_2 + \text{CH}_4$  feed and for pure  $\text{CO}_2$  and  $\text{CH}_4$  feeds. On pure  $\text{CO}_2$  conditions (Fig. S9) the intensity of atomic oxygen species, as observed at wavelengths of 777 nm ( $3s^5S^0 \rightarrow 3p^3P$ ) and 844 nm ( $3s^3S^0 \rightarrow 3p^3P$ ), was significantly lower in the zirconia-packed system compared to the plasma-only configuration, 3,807 au and 3,245 au (zirconia) versus 56,445 au and 59,645 au (plasma-only), respectively (see **Figure S9**). This reduction suggested that reactive oxygen species (ROS) were effectively mobilized from gas phase towards zirconia surface, consistent with heterogeneous kinetics wherein nearly most of the reaction occurs on solid surface.<sup>61</sup> When looking at the interactions of pure  $\text{CH}_4$  plasma and zirconia packed bed-Plasma, we observed a small reduction in the  $\text{CH}^*$  EOS signal, pointing that carbon species derived from  $\text{CH}_4$  plasma have little interaction with Zirconia, this small interaction was enough to increase the H signals more 2X. When a mixture of gasses is used, CO and H are the predominant species in the EOS analysis, increasing dramatically in zirconia-plasma system. Based on the experimental data, it was evident that  $\text{CO}^*$  (297 nm) and hydrogen-alpha (656.3 nm) surged significantly when feed composition changed from methane rich (1:2)  $\text{CO}_2:\text{CH}_4$  to equimolar and  $\text{CO}_2$  rich feed ratios, this trend was also reported by Devid et al<sup>62</sup>. (see **Figure 6**) This enhancement in reactive species correlated with a significant shift in product selectivity; for instance, the zirconia system yielded increased selectivity towards syngas further supported the conclusion that the zirconia altered the reaction pathway by enhancing the generation of specific gas-phase intermediates.

#### Plausible Plasma Activation (Gas Phase):

Electrons ( $e^-$ ) and excited species (\*) driven bond cleavage:


##### $\text{CO}_2$ Activation:

$\text{CO}_2 + e^- \rightarrow \text{CO}^* + \text{O}^*$  (General pathway, OES displays  $\text{CO}^*$  dominance)

$\text{CO}_2 \rightarrow \text{CO}_2^+ + e^-$  (Ionization)

##### $\text{CH}_4$ Activation:

$\text{CH}_4 + 3e^- \rightarrow \text{CH}^* + 3\text{H}^*$

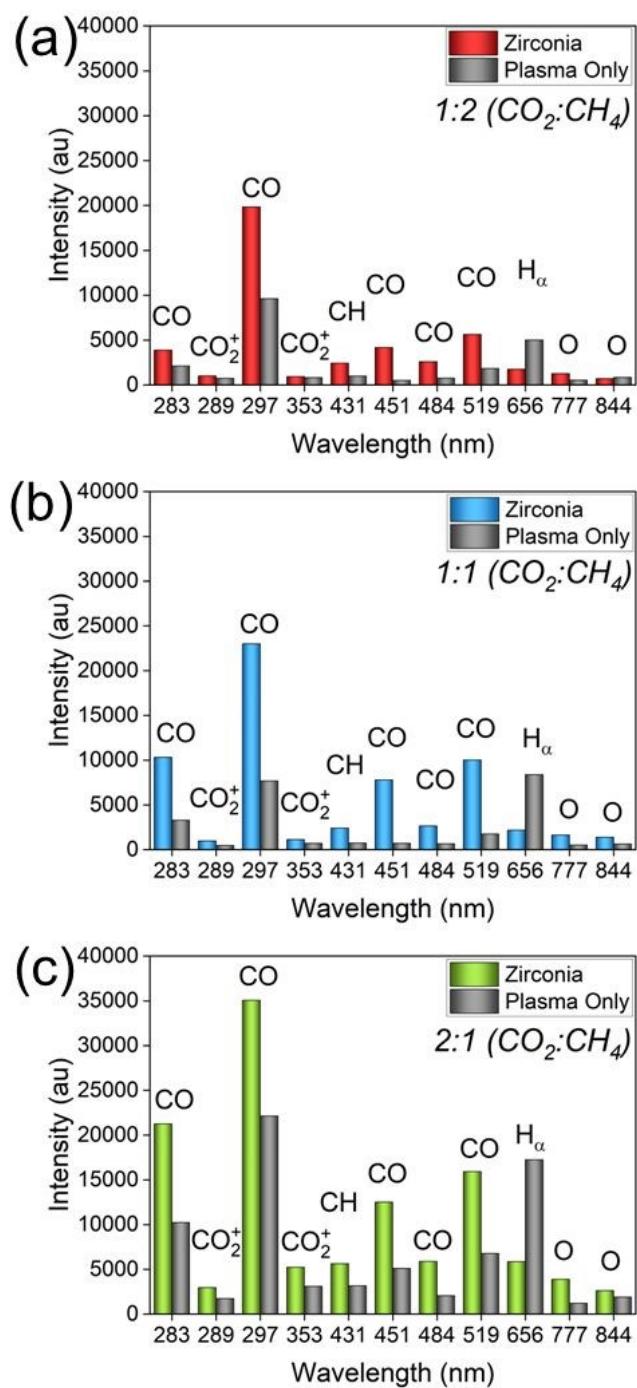

**Figure 6.** Dry methane reforming plasma-catalytic gas phase; (a) Methane rich feed 1:2 ( $\text{CO}_2:\text{CH}_4$ ); (b) Equimolar feed 1:1 ( $\text{CO}_2:\text{CH}_4$ ); (c) Carbon Dioxide rich feed 2:1 ( $\text{CO}_2:\text{CH}_4$ ); displaying important plasma species at various feed ratio ( $\text{CO}_2:\text{CH}_4$ ), and a total flow rate of 25 sccm, Plasma Power: 50 Watts, Reaction Time: 2 Hours.

## Surface Analysis

Gas phase analysis provided important insights. However, it is limited in its ability to fully characterize the material surface (Zirconia). To gain a complete understanding of the overall reaction, we performed Raman spectroscopy. After plasma treatment, the zirconia samples exhibited changes in Raman intensity. The bands at  $532\text{ cm}^{-1}$  (Zr–O stretching)<sup>63</sup> and  $560\text{ cm}^{-1}$  (oxide-vacancy vibration)<sup>64</sup> well defined in control (see Figure 7), disappeared after plasma exposure confirming the role of zirconia's oxygen mobility during DRM reaction. Further, we conducted XPS analysis, binding energies for zirconia before and after plasma exposure are presented in Table 2. In general, the binding energy (eV) reduced for zirconia after plasma exposure, the deconvoluted XPS analysis revealed that pure zirconia exhibited an O1s lattice oxygen (Zr–O) peak at 529.39 eV with a 43.9% area, whereas after plasma exposure the peak shifted to 529.11 eV with a 42.2% area (see Figure 8a,c.). This minor alteration indicated a modification in the lattice oxygen associated with the formation of oxygen vacancies. The surface hydroxyl (Zr–OH) component in the control sample was observed at 530.93 eV with a 56.0% area, shifting to 530.51 eV with a 42.9% area after plasma exposure, confirming the reduction of hydroxyl groups during the reaction (see Figure 8a, d). Interestingly, a new O1s peak appeared at 532.65 eV with a 14.8% area after plasma exposure, explicitly representing the formation of C–O species on the surface (see Figure 8a,c.).

Zr3d spectra represented the two split peaks which described the spin-orbit coupling, where the 3d electrons split into two distinct energy levels (5/2 and 3/2) for Zr<sup>4+</sup> state. An analysis of the Zr3d region demonstrated that the Zr3d<sub>5/2</sub> peak shifted from 181.59 eV with a 45.7% area in pure zirconia to 181.39 eV with a 50.1% area after plasma treatment, and the Zr3d<sub>3/2</sub> peak shifted from 183.92 eV

with a 54.2% area to 183.74 eV with a 49.8% area which may correspond to the changes in local rearrangements in Zr<sup>4+</sup> sites (see Figure 8b,d). Reported binding energies (eV) were consistent with literature values (see Table S2. for details).

Based on the observations it is confirmed that the RF plasma dry methane reforming slightly modified the zirconia surface. These modifications, in turn, supported increased oxygen mobility and accelerated the continuous removal and conversion of surface carbon to CO during the plasma catalytic dry reforming reaction.


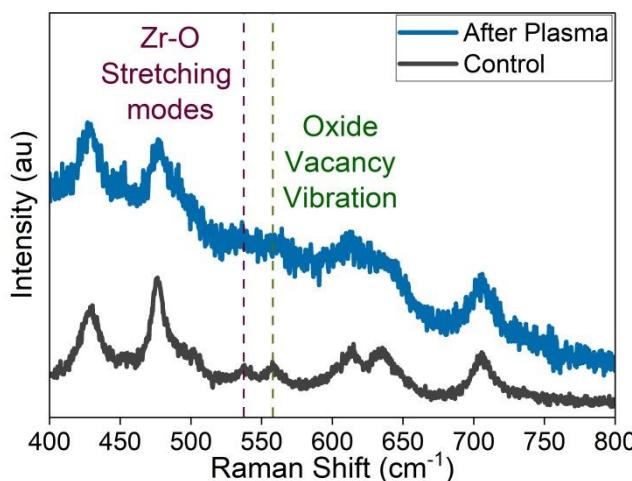


Figure 7. Comparative Raman spectra of zirconia samples demonstrating Zr–O stretching mode and oxide vacancy vibration features in control vs. sample exposed after plasma.

Table 2. Binding energy (eV) for the pure zirconia (control) Vs. after plasma exposure.


Species	Location	Binding	Control	Binding	After
		Energy	Zirconia	Energy	Plasma
		eV	% Area	eV	% Area
O1s	Zr–O	529.39	43.9	529.11	42.2
	Zr–OH	530.93	56.0	530.51	42.9
	C–O	-	-	532.65	14.8
Zr3d	Zr3d <sub>5/2</sub>	181.59	45.7	181.39	50.1
	Zr3d <sub>3/2</sub>	183.92	54.2	183.74	49.8

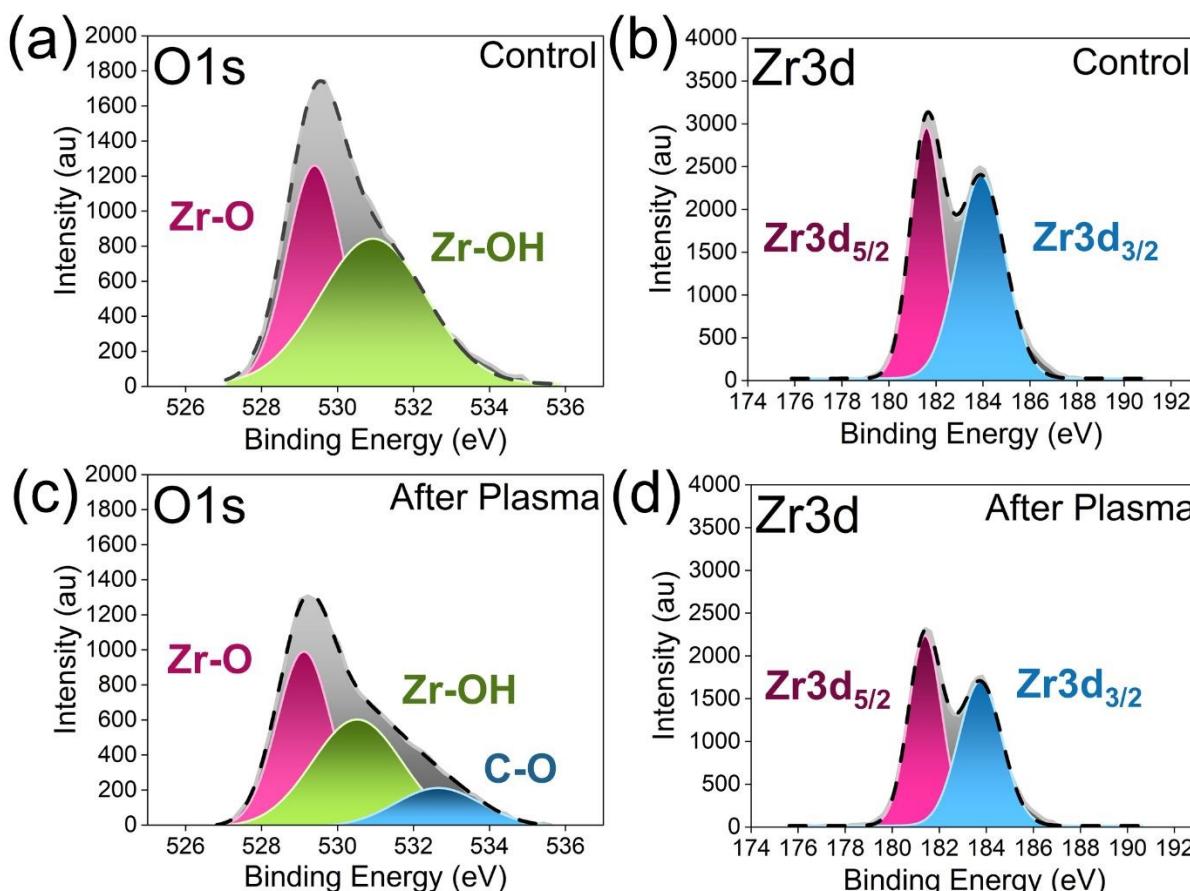

**Figure 8.** Comparative X-ray Photoelectron Spectroscopy (XPS) analysis of zirconia surfaces; Panels (a-b) display spectra for pure zirconia (Control): (a) O1s, (b) Zr3d; Panels (c-d) describing to zirconia after plasma exposure: (c) O1s, (d) Zr3d.

#### State of the Art and Plausible Mechanism

While comparing the presented results with the literature, it is important to mention in the literature various plasma sources were evaluated for DRM over a wide range of applied powers at equimolar feed ratio from low power plasma sources DBD (7-40 Watts)<sup>12, 13, 16, 69, 70</sup> to high power sources RF plasma (25-150 Watts)<sup>62</sup>, Gliding Arc (GA)<sup>71</sup> with 165 Watts, and Microwave (MW)<sup>72, 73</sup> with 1000-3000 Watts, without catalysts and additional packing materials. In our presented work low-power radiofrequency (RF) plasma at 50 W without any catalyst achieved CH<sub>4</sub> and CO<sub>2</sub> conversions of 16.5% and 11.9%, respectively. Plasma material synergy plays an integral role in enhancing the methane and carbon dioxide conversions. Moreover, it has been demonstrated by various researchers that transition metals on alumina,<sup>74,70</sup> silica,<sup>75</sup> zeolites<sup>70</sup> and MOFs<sup>13</sup> DMR can be selectively controlled towards desired products. However, it is important to note that due to limited resources and growing urgency for rare earth metals, researchers are focussing on improving design and incorporating earth abundant materials.<sup>18, 76</sup> Herein, a highly stable material such as zirconia was introduced at low power (50 W), enhancing the conversions markedly to 63.7% for CH<sub>4</sub> and 57.1% for CO<sub>2</sub> (see Figure 9 and Table S3).

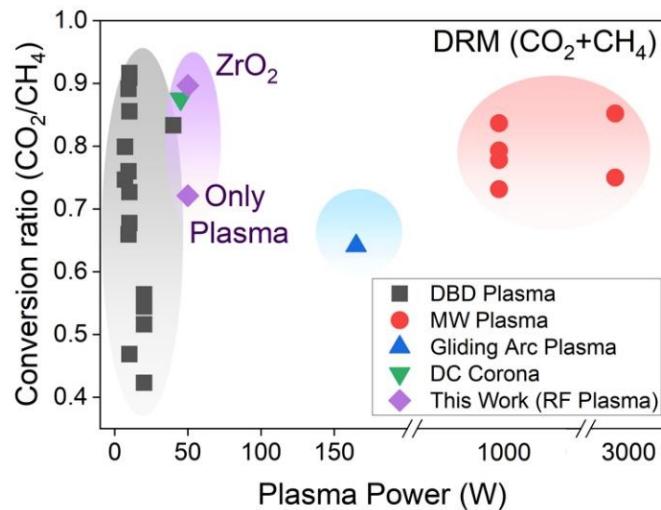

**Figure 9.** State of the art plasma-catalytic dry reforming of methane, comparison of (CO<sub>2</sub>/CH<sub>4</sub>) conversion ratio vs. applied plasma power (Watts) for DBD,<sup>12, 13, 16, 69, 70</sup> MW,<sup>72, 73</sup> GA,<sup>71</sup> DC<sup>77</sup> and this work with RF plasma at low power.

## ARTICLE

## Journal Name

It is well noted that major reactions in heterogenous catalysis occurs on the surface.<sup>61</sup> In this work, zirconia's surface reactions played a critical role in enabling syngas formation due to the presence of oxygen vacancies ( $V_o$ ) facilitating the mobility of atomic oxygen.

On the surface the reaction initiates with  $\text{CO}_2$  splitting, where  $\text{CO}_2$  in gas phase interacted with a zirconia vacancy, leading to the formation of surface adsorbed CO and O species. In order to confirm, we compared the signatures of plasma only and zirconia surface when using pure  $\text{CO}_2$  OES, interestingly we observed the intensities of the atomic oxygen were extremely high in plasma only and drastically reduced with zirconia packed system, which implies higher adsorption of atomic oxygen on the zirconia surface. (see Figure S9 a, b in supplementary information). Based on the measured species of gas phase via OES we hypothesize that firstly, methane underwent dehydrogenation, dissociating into  $\text{CH}$  radicals, and atomic hydrogen. On the zirconia surface, the gas phase exhibited stronger  $\text{CH}^*$  (431 nm) signatures compared to plasma only and looking at the selectivity we can observe higher recombination of methane derived active species in plasma only system. On the other hand atomic hydrogen (656.3 nm) levels were lower than in plasma only conditions. This implies a higher recombination of hydrogen in the zirconia-plasma system pointing the impact of the catalyst-plasma synergistic effect in DMR.


A pathway to mitigate coking in zirconia's surface atomic carbon could react with atomic oxygen to produce CO in gas phase, the oxygen migration increases due to the presence of vacancies ( $V_o$ ) and oxygen species consume can be replenish. Finally, hydrogen atoms recombine to form molecular hydrogen ( $\text{H}_2$  formation). These surface reactions cooperatively improved the syngas formation. (see Figure 10)

## Plausible Surface Reactions on Zirconia

## Conclusions

In this study, we explored the plasma catalytic dry methane reforming at minimal plasma power (50 watts). This study demonstrated the significant impact of a zirconia-packed bed on plasma-assisted dry reforming of methane (plasma-DRM). Based on the experimental results introducing zirconia into plasma driven  $\text{CO}_2/\text{CH}_4$  conversion significantly improves performance. Under plasma-only conditions,  $\text{CH}_4$  and  $\text{CO}_2$  conversions were 16.5% and 12.0%. Nonetheless, packing the reactor with an inert material such as fumed silica elevated these conversions to 38.4% for  $\text{CH}_4$  and 23.4% for  $\text{CO}_2$ . However, when zirconia ( $\text{ZrO}_2$ ) was packed, the enhancements were even more evident, with methane conversion increased to 63.7% and  $\text{CO}_2$  conversion reached 57.2%. The plasma zirconia synergy facilitated  $\text{CO}_2$  decomposition generating CO and oxygen active species increasing syngas (CO and  $\text{H}_2$ ) yields while reducing heavier alkanes and oxygenates. At equimolar feed composition, the CO selectivity rose from 39.5% to 46.5%, and  $\text{H}_2$  selectivity increased from 23.7 % to 27.5%. The feed composition methane rich 1:2 ( $\text{CO}_2:\text{CH}_4$ ) lead to lower conversions due to possible methane recombination on the other hand, with  $\text{CO}_2$  rich 2:1 ( $\text{CO}_2:\text{CH}_4$ ) revealed the best conversions mitigating the possible

Zirconia's oxygen vacancies ( $V_o$ ) and mobility of O atoms drive syngas formation (see Figure 10). [View Article Online](#) DOI: 10.1039/DSEY00069F

CO<sub>2</sub> Splitting:CH<sub>4</sub> Dehydrogenation:

## Carbon Renewal:


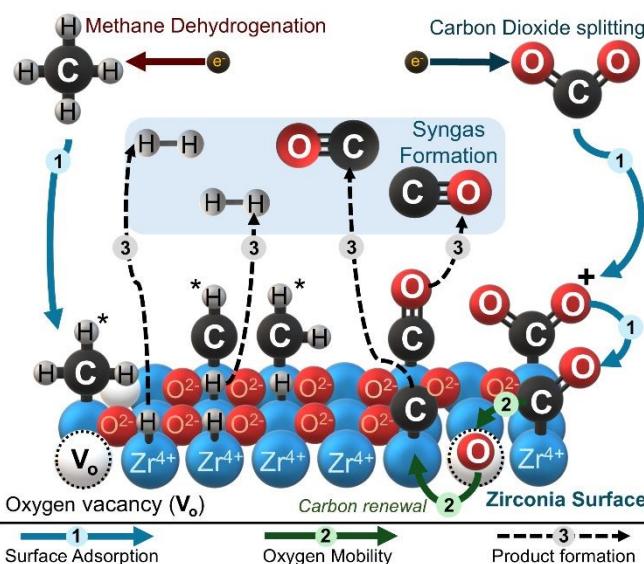

H<sub>2</sub> Formation:

Figure 10. Plausible plasma catalytic pathway for mitigating coking on the zirconia ( $\text{ZrO}_2$ ) surface.

methane recombination and leading to higher syngas formation. Optical emission spectroscopy (OES) confirmed that zirconia dramatically increase the CO concentrations in the gas bulk and also favored reactive atomic oxygen species in the gas phase. Stability tests over six hours of plasma operation at 50 W showed no significant changes in zirconia's properties or plasma-catalytic performance, confirming its robustness. In conclusion, Zirconia significantly enhanced plasma DRM efficiency, increasing conversion and syngas production while providing understandings for sustainable low temperature plasma DRM systems.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

Maria L. Carreon acknowledges NSF-CAREER award No. 2235247.

## References

1. D. Pakhare and J. Spivey, *Chemical Society Reviews*, 2014, **43**, 7813-7837.
2. C. Palmer, D. C. Upham, S. Smart, M. J. Gordon, H. Metiu and E. W. McFarland, *Nature Catalysis*, 2020, **3**, 83-89.
3. M. L. Carreon, *Nature Catalysis*, 2025, **8**, 2-7.
4. T. Nozaki, D.-Y. Kim and X. Chen, *Japanese Journal of Applied Physics*, 2024, **63**, 030101.
5. D.-Y. Kim, H. Ham, X. Chen, S. Liu, H. Xu, B. Lu, S. Furukawa, H.-H. Kim, S. Takakusagi and K. Sasaki, *Journal of the American Chemical Society*, 2022, **144**, 14140-14149.
6. S. Kameshima, K. Tamura, Y. Ishibashi and T. Nozaki, *Catalysis Today*, 2015, **256**, 67-75.
7. T. Nozaki, A. Ağiral, S. Yuzawa, J. G. E. H. Gardeniers and K. Okazaki, *Chemical engineering journal*, 2011, **166**, 288-293.
8. H. M. Nguyen, F. Gorky, S. Guthrie, J. M. Crawford, M. A. Carreon, J. B. Jasinski and M. L. Carreon, *Energy Conversion and Management*, 2023, **286**, 117082.
9. Y. Ma, X. Han, S. Xu, Z. Li, W. Lu, B. An, D. Lee, S. Chansai, A. M. Sheveleva and Z. Wang, *Journal of the American Chemical Society*, 2023, **145**, 20792-20800.
10. P. Navascués, J. Cotrino, A. R. González-Elipe and A. Gómez-Ramírez, *Fuel Processing Technology*, 2023, **248**, 107827.
11. P. Chawdhury, Y. Wang, D. Ray, S. Mathieu, N. Wang, J. Harding, F. Bin, X. Tu and C. Subrahmanyam, *Applied Catalysis B: Environmental*, 2021, **284**, 119735.
12. Y. Wang, Y. Chen, J. Harding, H. He, A. Bogaerts and X. Tu, *Chemical Engineering Journal*, 2022, **450**, 137860.
13. F. Gorky, A. Nambo and M. L. Carreon, *Journal of CO<sub>2</sub> Utilization*, 2021, **51**, 101642.
14. W. Wang, R. Snoeckx, X. Zhang, M. S. Cha and A. Bogaerts, *The Journal of Physical Chemistry C*, 2018, **122**, 8704-8723.
15. X. Tu and J. C. Whitehead, *Applied Catalysis B: Environmental*, 2012, **125**, 439-448.
16. L. Wang, Y. Yi, C. Wu, H. Guo and X. Tu, *Angewandte Chemie*, 2017, **129**, 13867-13871.
17. D. Mei, X. Zhu, Y.-L. He, J. D. Yan and X. Tu, *Plasma Sources Science and Technology*, 2014, **24**, 015011.
18. R. Bellabarba, P. Johnston, S. Moss, C. Sievers, B. Subramaniam, C. Tway, Z. Wang and H. Zhu, *ACS Catalysis*, 2023, **13**, 7917-7928.
19. Z. Li, S. Das, P. Hongmanorom, N. Dewangan, M. H. Wai and S. Kawi, *Catalysis Science & Technology*, 2018, **8**, 2763-2778.
20. J. Newnham, K. Mantri, M. H. Amin, J. Tardio and S. K. Bhargava, *International journal of hydrogen energy*, 2012, **37**, 1454-1464.
21. P. Kumar, Y. Sun and R. O. Idem, *Energy & fuels*, 2007, **21**, 3113-3123.
22. G. D. Yadav and J. J. Nair, *Microporous and mesoporous materials*, 1999, **33**, 1-48. [View Article Online](#) DOI: 10.1039/DSEY00069F
23. D. Liu, X. Y. Quek, W. N. E. Cheo, R. Lau, A. Borgna and Y. Yang, *Journal of Catalysis*, 2009, **266**, 380-390.
24. Ş. Özkar-Aydinoğlu, E. Özensoy and A. E. Aksoyulu, *international journal of hydrogen energy*, 2009, **34**, 9711-9722.
25. A. S. A. Al-Fatesh, A. H. Fakieha and A. E. Abasaeed, *Chinese Journal of Catalysis*, 2011, **32**, 1604-1609.
26. M. Nizio, A. Albarazi, S. Cavadias, J. Amouroux, M. E. Galvez and P. Da Costa, *International Journal of Hydrogen Energy*, 2016, **41**, 11584-11592.
27. R. Snoeckx and A. Bogaerts, *Chemical Society Reviews*, 2017, **46**, 5805-5863.
28. H. Puliyalil, D. L. Jurković, V. D. B. C. Dasireddy and B. Likozar, *RSC advances*, 2018, **8**, 27481-27508.
29. S. Liu, L. R. Winter and J. G. Chen, *ACS Catalysis*, 2020, **10**, 2855-2871.
30. R. Benrabbah, C. Cavanoli, H. Liu, S. Ognier, S. Cavadias, M. E. Gálvez and P. Da Costa, *Catalysis Communications*, 2017, **89**, 73-76.
31. M. Nizio, R. Benrabbah, M. Krzak, R. Debek, M. Motak, S. Cavadias, M. E. Gálvez and P. Da Costa, *Catalysis Communications*, 2016, **83**, 14-17.
32. J. R. Shah, F. Gorky, J. Lucero, M. A. Carreon and M. L. Carreon, *Industrial & Engineering Chemistry Research*, 2020, **59**, 5167-5176.
33. J. Shah, F. Gorky, P. Psarras, B. Seong, D. A. Gómez-Gualdrón and M. L. Carreon, *ChemCatChem*, 2020, **12**, 1200-1211.
34. F. Gorky, J. M. Lucero, J. M. Crawford, B. A. Blake, S. R. Guthrie, M. A. Carreon and M. L. Carreon, *Catalysis Science & Technology*, 2021, **11**, 5109-5118.
35. F. Gorky, A. Best, J. Jasinski, B. J. Allen, A. C. Alba-Rubio and M. L. Carreon, *Journal of Catalysis*, 2021, **393**, 369-380.
36. F. Gorky, J. M. Lucero, J. M. Crawford, B. Blake, M. A. Carreon and M. L. Carreon, *ACS Applied Materials & Interfaces*, 2021, **13**, 21338-21348.
37. F. Gorky, S. R. Guthrie, C. S. Smoljan, J. M. Crawford, M. A. Carreon and M. L. Carreon, *Journal of Physics D: Applied Physics*, 2021, **54**, 264003.
38. H. M. Nguyen, F. Gorky, S. Guthrie and M. L. Carreon, *Catalysis Today*, 2023, **418**, 114141.
39. F. Gorky, A. Nambo, T. J. Kessler, J. H. Mack and M. L. Carreon, *Industrial & Engineering Chemistry Research*, 2023, **62**, 19571-19584.
40. H. M. Nguyen and M. L. Carreon, *ACS Sustainable Chemistry & Engineering*, 2022, **10**, 9480-9491.
41. J. Shah, J. Lopez-Mercado, M. G. Carreon, A. Lopez-Miranda and M. L. Carreon, *ACS omega*, 2018, **3**, 455-463.
42. F. Gorky, V. Storr, G. Jones, A. Nambo, J. B. Jasinski and M. L. Carreon, *Membranes*, 2024, **14**, 178.
43. F. Gorky, H. M. Nguyen, K. Krishnan, J. M. Lucero, M. L. Carreon and M. A. Carreon, *ACS Applied Energy Materials*, 2023, **6**, 4380-4389.
44. J. Shah, F. Gorky, P. Psarras, B. Seong, D. A. Gómez-Gualdrón and M. L. Carreon, *ChemCatChem*, 2020, **12**, 1200-1211.
45. S. Gershman, H. Fetsch, F. Gorky and M. L. Carreon, *Plasma Chemistry and Plasma Processing*, 2022, **42**, 731-757.
46. J. R. Shah, J. M. Harrison and M. L. Carreon, *Catalysts*, 2018, **8**, 437.



## ARTICLE

47. J. Shah, P. Ratnasamy and M. L. Carreon, *Catalysts*, 2017, **7**, 372.

48. F. Gorky, M. A. Carreon and M. L. Carreon, *IOP SciNotes*, 2020, **1**, 024801.

49. J. Shah, T. Wu, J. Lucero, M. A. Carreon and M. L. Carreon, *ACS Sustainable Chemistry & Engineering*, 2018, **7**, 377-383.

50. F. Gorky, H. M. Nguyen, J. M. Lucero, S. Guthrie, J. M. Crawford, M. A. Carreon and M. L. Carreon, *Chemical Engineering Journal Advances*, 2022, 100340.

51. A. Midilli, H. Kucuk, M. E. Topal, U. Akbulut and I. Dincer, *International Journal of Hydrogen Energy*, 2021, **46**, 25385-25412.

52. A. Vita, G. Cristiano, C. Italiano, L. Pino and S. Specchia, *Applied Catalysis B: Environmental*, 2015, **162**, 551-563.

53. Y. Zhang, H. Qin, Y. Long, A. Cao, K. Wang, L. Gao, Z. Zhao, H. Zhang, H. Zhang and J. Yan, *Applied Catalysis B: Environment and Energy*, 2025, **371**, 125206.

54. Y. Long, X. Wang, H. Zhang, K. Wang, W.-L. Ong, A. Bogaerts, K. Li, C. Lu, X. Li and J. Yan, *JACS Au*, 2024, **4**, 2462-2473.

55. P. Aldebert and J. P. Traverse, *Journal of the American Ceramic Society*, 1985, **68**, 34-40.

56. S. Damyanova, B. Pawelec, K. Arishtirova, M. V. M. Huerta and J. L. G. Fierro, *Applied Catalysis A: General*, 2008, **337**, 86-96.

57. X. Song, Y. Ding, J. Zhang, C. Jiang, Z. Liu, C. Lin, W. Zheng and Y. Zeng, *Journal of Materials Research and Technology*, 2023, **23**, 648-655.

58. M. O. Zacate, L. Minervini, D. J. Bradfield, R. W. Grimes and K. E. Sickafus, *Solid State Ionics*, 2000, **128**, 243-254.

59. M. Thommes, K. Kaneko, A. V. Neimark, J. P. Olivier, F. Rodriguez-Reinoso, J. Rouquerol and K. S. W. Sing, *Pure and applied chemistry*, 2015, **87**, 1051-1069.

60. A. Trovarelli, *Catalysis by ceria and related materials*, World Scientific, 2002.

61. I. Langmuir, *Transactions of the Faraday Society*, 1922, **17**, 607-620.

62. E. Devid, D. Zhang, D. Wang, M. Ronda-Lloret, Q. Huang, G. Rothenberg, N. R. Shiju and A. W. Kleyn, *Energy Technology*, 2020, **8**, 1900886.

63. A. E. Pasto and R. A. Condrate Sr, *Journal of the American Ceramic Society*, 1973, **56**, 436-438.

64. Y. B. Rajput, A. S. Al-Fatesh, A. I. Osman, M. O. Bayazed, A. A. Ibrahim, A. H. Fakieha, A. E. Abasaeed, F. S. Almubaddel, O. Alothman and R. Kumar, *Fuel*, 2024, **378**, 132843.

65. A. Bumajdad, A. A. Nazeer, F. Al Sagheer, S. Nahar and M. I. Zaki, *Scientific reports*, 2018, **8**, 3695.

66. H. Gu, J. Ding, Q. Zhong, Y. Zeng and F. Song, *international journal of hydrogen energy*, 2019, **44**, 11808-11816.

67. S. R. Teeparthi, E. W. Awin and R. Kumar, *Scientific reports*, 2018, **8**, 5541.

68. X. Chen, X. Wang and D. Fang, *Fullerenes, Nanotubes and Carbon Nanostructures*, 2020, **28**, 1048-1058.

69. D. Li, V. Rohani, F. Fabry, A. P. Ramaswamy, M. Sennour and L. Fulcheri, *Applied Catalysis B: Environmental*, 2020, **261**, 118228.

70. K. Krawczyk, M. Młotek, B. Ulejczyk and K. Schmidt-Szałowski, *Fuel*, 2014, **117**, 608-617.

71. X. Tu and J. C. Whitehead, *International journal of hydrogen energy*, 2014, **39**, 9658-9669.

72. S. Kelly, E. Mercer, R. De Meyer, R.-G. Ciocarlan, S. Bals and A. Bogaerts, *Journal of CO<sub>2</sub> Utilization*, 2023, **75**, 102564F

73. S. M. Chun, D. H. Shin, S. H. Ma, G. W. Yang and Y. C. Hong, *Catalysts*, 2019, **9**, 292.

74. L. Wang, Y. Yi, C. Wu, H. Guo and X. Tu, *Angew. Chem. Int. Ed.*, 2017, **56**, 13679-13683.

75. D. Li, V. Rohani, F. Fabry, A. P. Ramaswamy, M. Sennour and L. Fulcheri, *Appl. Catal. B*, 2020, **261**, 118228.

76. F. Gorky, V. Storr, J. B. Jasinski and M. L. Carreon, *ACS Materials Au*, 2025.

77. M.-w. Li, G.-h. Xu, Y.-l. Tian, L. Chen and H.-f. Fu, *The Journal of Physical Chemistry A*, 2004, **108**, 1687-1693.



# Leveraging Oxygen Mobility with Zirconia in Low-Temperature Plasma for Enhanced Methane Reforming to Syngas

FNU Gorky,<sup>a</sup> Levi Pile,<sup>a</sup> Grace Jones,<sup>a</sup> Apolo Nambo,<sup>b</sup> Mourad Benamara,<sup>c</sup> and Maria L. Carreon<sup>a,†</sup>

<sup>a</sup> Ralph E. Martin Department of Chemical Engineering, University of Arkansas, 3202 Bell Engineering Center, Fayetteville, Arkansas 72701-1201, United States.

<sup>b</sup> Bert Thin Films, LLC., 625 Myrtle St, Louisville, KY 40298, USA.

<sup>†</sup> Corresponding author: Maria L. Carreon; Email: mc138@uark.edu

## Data Availability

Data supporting the findings of this study are available within the article and its Supporting Information files. Additional data can be provided by the authors upon reasonable request.

