

OPEN ACCESS

Communication — The Impact of Co-solvent Selection for Dimethyl-2,5-dioxahexane carboxylate in Sodium Ion Batteries

To cite this article: Rishivandhiga Jayakumar *et al* 2024 *ECS Adv.* **3** 020504

View the [article online](#) for updates and enhancements.

You may also like

- [Semi-Analytical Methodology to Correct Polarization Curve to Measure Tafel Slope for an Electronic Resistance Laden Catalyst Layer](#)

Yadul Sethi, Yan-Sheng Li and Bharatkumar Suthar

- [Electrochemical Sensing of Phenylbutazone using Multi-Walled Carbon Nanotube Paste Electrode in Pharmaceutical and Biological Fluids](#)

Yuvarajgouda Patil, Manjunath Megalamani, Jyothi Abbar *et al.*

- [Self-Activated SiO₂/C Nanocomposite from Silica-Rich Marine Mucilage for Supercapacitor Applications](#)

Neriman Sinan Tatlı, Mete Yılmaz and Ece Unur Yılmaz

ECC-Opto-10 Optical Battery Test Cell: Visualize the Processes Inside Your Battery!

EL-CELL®
electrochemical test equipment





- ✓ **Battery Test Cell for Optical Characterization**
Designed for light microscopy, Raman spectroscopy and XRD.
- ✓ **Optimized, Low Profile Cell Design (Device Height 21.5 mm)**
Low cell height for high compatibility, fits on standard sample stages.
- ✓ **High Cycling Stability and Easy Handling**
Dedicated sample holders for different electrode arrangements included!
- ✓ **Cell Lids with Different Openings and Window Materials Available**



Scan me!

Contact us:

- 📞 +49 40 79012-734
- ✉️ sales@el-cell.com
- 🌐 www.el-cell.com

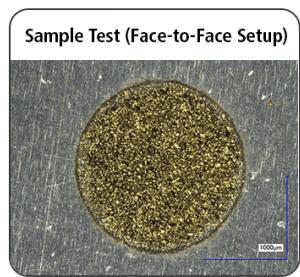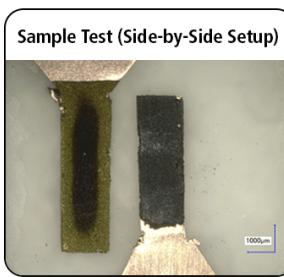



Communication — The Impact of Co-solvent Selection for Dimethyl-2,5-dioxahexane carboxylate in Sodium Ion Batteries

Rishivandhiga Jayakumar,^{1,2} Vadim Shipitsyn,^{1,2,*} Chanmonirath (Michael) Chak,^{1,2} Wenhua Zuo,³ Bing Sun,⁴ Xiaochuan Lu,⁵ and Lin Ma^{1,2,***,z} 

¹Department of Mechanical Engineering and Engineering Science, The University of North Carolina at Charlotte, Charlotte, North Carolina 28223, United States of America

²Battery Complexity, Autonomous Vehicle and Electrification (BATT CAVE) Research Center, The University of North Carolina at Charlotte, Charlotte, North Carolina 28223, United States of America

³Chemical Sciences and Engineering Division, Argonne National Laboratory, Lemont, Illinois 60439 United States of America

⁴Centre for Clean Energy Technology, School of Mathematical and Physical Sciences, Faculty of Science, University of Technology Sydney, Ultimo, NSW, 2007, Australia

⁵Department of Applied Engineering Technology, North Carolina A&T State University, Greensboro, North Carolina 27411, United States of America

Traditional linear carbonates including dimethyl carbonate (DMC), diethyl carbonate (DEC), and ethyl methyl carbonate (EMC) were investigated as co-solvents for the dimethyl-2,5-dioxahexane carboxylate (DMOHC)-based electrolyte in $\text{Na}_{0.97}\text{Ca}_{0.03}[\text{Mn}_{0.39}\text{Fe}_{0.31}\text{Ni}_{0.22}\text{Zn}_{0.08}]\text{O}_2$ (NCMFNZO)/hard carbon (HC) pouch cells. The EMC-containing cell displays excellent electrochemical performance, exhibiting only a 1.6 mAh irreversible capacity loss during 500 h of storage at 4 V and 40 °C, and maintaining over 80% capacity retention after 200 cycles up to 4 V at 40 °C. Severe gas evolution and Na plating issues are present in all the tested systems.

© 2024 The Author(s). Published on behalf of The Electrochemical Society by IOP Publishing Limited.. This is an open access article distributed under the terms of the Creative Commons Attribution 4.0 License (CC BY, <http://creativecommons.org/licenses/by/4.0/>), which permits unrestricted reuse of the work in any medium, provided the original work is properly cited. [DOI: [10.1149/2754-2734/ad4e48](https://doi.org/10.1149/2754-2734/ad4e48)]



Manuscript submitted February 25, 2024; revised manuscript received April 5, 2024. Published May 29, 2024.

The lifetime of sodium ion batteries (SIBs) still cannot meet the application requirements in grid energy storage systems, preventing them from serving as a viable alternative to lithium-ion batteries (LIBs).^{1,2} Tuning the electrolyte components is considered as an effective way to promote the interphasial chemistries and properties which can mitigate side reactions between electrodes and electrolytes and extend cell lifetime.^{3,4} Significant recent attention has been dedicated to electrolyte engineering in SIBs with the goal of extending cell lifespan.⁵⁻⁸ Being different from the reported solvent chemistries, recent studies by Taskovic et al.^{9,10} have demonstrated that the use of dimethyl-2,5-dioxahexane carboxylate (DMOHC, Fig. 1) as the solvent can dramatically improve the lifetime of LiFePO_4 /graphite (LFP) and $\text{Li}[\text{Ni}_{0.5}\text{Mn}_{0.3}\text{Co}_{0.2}]\text{O}_2$ /graphite cells. However, DMOHC's functionality is constrained to high temperatures (>70 °C) due to its high viscosity (i.e. 6.93 cP at 25 °C).⁵ It's important to note that not every battery necessitates operation in such a high temperature environment. The incorporation of co-solvents into DMOHC becomes essential to reduce viscosity, enabling functionality without the need for extreme temperatures. Traditional linear carbonates (Fig. 1), such as dimethyl carbonate (DMC), diethyl carbonate (DEC), and ethyl methyl carbonate (EMC), are commonly employed as co-solvents with low viscosity (i.e. DMC: 0.59 cP at 20 °C, EMC: 0.65 cP at 25 °C, DEC: 0.75 cP at 25 °C) to modulate electrolyte bulk properties.^{9,11,12} Komaba et al.¹³ studied the influence of these co-solvents on the electrochemical performance of a hard carbon (HC) anode when combined with ethylene carbonate (EC). However, limited studies exist on the impact of DMOHC on cell electrochemical performance when mixed with various co-solvents in SIBs.

By utilizing $\text{Na}_{0.97}\text{Ca}_{0.03}[\text{Mn}_{0.39}\text{Fe}_{0.31}\text{Ni}_{0.22}\text{Zn}_{0.08}]\text{O}_2$ (NCMFNZO)/HC pouch cells, we studied the cell electrochemical performance with different DMOHC-based electrolytes when DMC, DEC, and EMC served as co-solvents. Our results suggest increased sodium inventory

loss during long-term cycling when DMC was employed as a co-solvent.

Experimental

Factory-manufactured 210 mAh NCMFNZO/HC pouch cells, without electrolyte, were obtained from Lifun Technology (Zhuzhou, Hunan, China). Detailed cell information can be referred to the previous reports.^{14,15} According to 1:1 volume ratio, DMOHC (>98%, $\text{H}_2\text{O} < 20$ ppm, TCI) was mixed with selected co-solvents (>99.5%, $\text{H}_2\text{O} < 20$ ppm, CapChem) including EMC, DEC and DEC to form 1 m NaPF_6 (> 98.0%, $\text{H}_2\text{O} < 20$ ppm, TCI) electrolytes. 2% fluoroethylene carbonate ((FEC), >99.5%, $\text{H}_2\text{O} < 20$ ppm, Gotion) was used as an electrolyte additive in all the electrolytes. The procedure of pouch cell formation and scanning electron microscopy (SEM) testing are consistent with previous work.¹⁵ After the formation, the cells were discharged to 1.5 V and charged to 4.0 V twice using C/20 at 40 °C before the 500 h storage at open circuit voltage. Cells were cycled after storage according to the previous procedure at 40 °C.¹⁵ The amount of gas generated in the cells during formation, storage and cycling was determined through the application of Archimedes' principle, as detailed in the work by Aiken et al.¹⁶ The electrochemical impedance spectroscopy (EIS) data, collected using a Biologic VMP3, involved ten data points per decade within the frequency range of 100 kHz to 100 mHz. The signal amplitude was set at 10 mV, and the measurements were conducted at 25 °C.

Results and Discussion

The effect of different linear carbonate co-solvents on the cell formation was quantified by gas volume evolution (Fig. 2A) and charge transfer resistance (R_{ct} , Fig. 2B). All the EIS spectra were measured at 3.1 V and room temperature. 2% FEC was added as a film-forming electrolyte additive in each cell. During cell formation at 40 °C with an upper cut-off voltage of 4 V, DMC generates more gas than DEC and EMC. According to the Nyquist plot with equivalent circuit fitting (Fig. 2B), the R_{ct} of DMC containing cell is much smaller compared to that of DEC and EMC after formation.

*Electrochemical Society Student Member.

**Electrochemical Society Member.

^zE-mail: l.ma@charlotte.edu

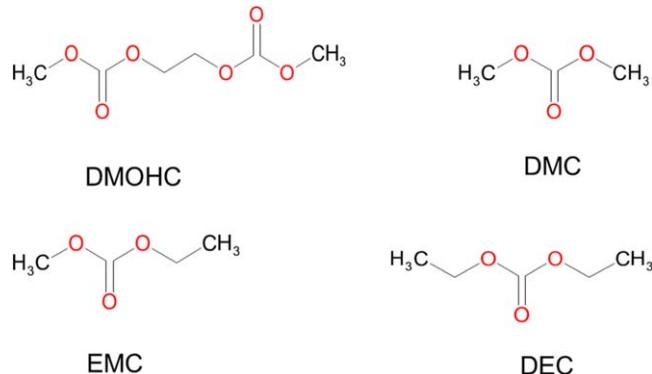


Figure 1. Chemical structures of selected solvents.

After formation, the cells were cycled twice at C/20 before storing under open circuit conditions for the next 500 h at 4.0 V and 40 °C. After 500 h of storage, the storage cells underwent two additional cycles with a current applied at C/20 to evaluate the extent of capacity loss experienced during the storage period. The critical parameters outlined by Sinha et al.¹⁷ for a storage test include the discharge capacity before storage (D_0), the discharge capacity immediately after storage (D_1), the discharge capacity of a fully charged cell after storage (D_2), and the voltage drop (V_{drop}) during storage, as illustrated in Fig. 2C. According to Sinha et al.,¹⁷ D_1 starts with the smallest capacity and at the lowest potential, attributable to the storage interval. D_2 , featuring a larger capacity than D_1 , suggests the recovery of some reversible capacity loss during storage. However, D_2 displays a smaller capacity than D_0 , indicating irreversible capacity loss. In Table I, the EMC containing cell shows the smallest irreversible capacity (D_0-D_2) compared to that of DEC and DMC. Figure 2D shows that the EMC containing cell has the least potential variations during the open circuit 500 h storage at 40 °C. Per the Li inventory model by Sinha et al.,¹⁷ this suggests that the inclusion of EMC may suppress electrolyte oxidation and potential shuttles, potentially facilitating the formation of a stable cathode electrolyte interphase (CEI).

The volume of gas evolution was recorded after 500 h storage at 40 °C as shown in Fig. 2E. Regardless of the chosen co-solvents, significant gas production was observed in all cells. Figure 2F shows the post-storage Nyquist plot of the cells in Fig. 2B. R_{ct} of EMC containing cells only increased by 43.68 $\Omega \cdot \text{cm}^2$ after storage, a smaller change compared to DMC (57.46 $\Omega \cdot \text{cm}^2$) and DEC (71.93 $\Omega \cdot \text{cm}^2$) containing cells.

In order to test the effect of selected co-solvents on the cycling lifetime of these SIBs, the pouch cells after storage were tested between 1.5 and 4.0 V at 40 °C and C/3 with C/20 check-up cycles every 50 cycles. Figure 3 shows the discharge capacity (A), and voltage polarization (B) as a function of cycle number for various co-solvent-containing cells. The capacity retention ranking is EMC>DEC>DMC (Fig. 3A), which is consistent with previous storage testing (Fig. 2D). All the cells tested here show a capacity retention >80% after 200 cycles (Fig. 3A). Surprisingly, the DMC containing cell shows slower polarization growth compared to DEC and EMC containing cells during cycling (Fig. 3B). Figure 3C shows the post-cycling Nyquist plot of the cells in Figs. 3A–3B. R_{ct} of DMC containing cell ($222 \Omega \cdot \text{cm}^2$) is smaller compared to EMC ($274.5 \Omega \cdot \text{cm}^2$) and DEC ($302.5 \Omega \cdot \text{cm}^2$) containing cells, aligning with the results in Fig. 3B. To identify the reason for the lower

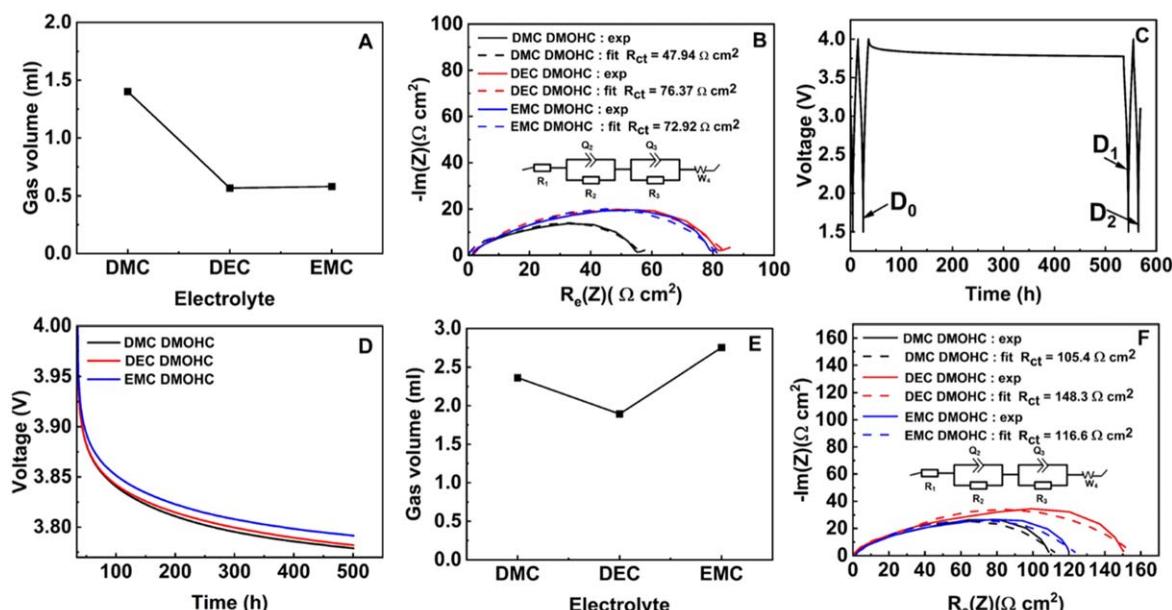


Figure 2. Evaluation of the effects of co-solvents during formation and storage. (A) Gas evolution during cell formation; (B) the Nyquist plot after cell formation measured at 3.1 V and room temperature; (C) a schematic of storage testing voltage vs. time profile; (D) voltage vs. time during 500 h storage testing at 40 °C and 4 V; (E) gas evolution during 500 h storage testing; (F) the Nyquist plot after cell 500 h storage testing measured at 3.1 V and room temperature. In the equivalent circuit model, Q is constant phase element, W is Warburg diffusion element, R_1 is solution resistance, R_2 is charge transfer resistance, R_3 is contact resistance.

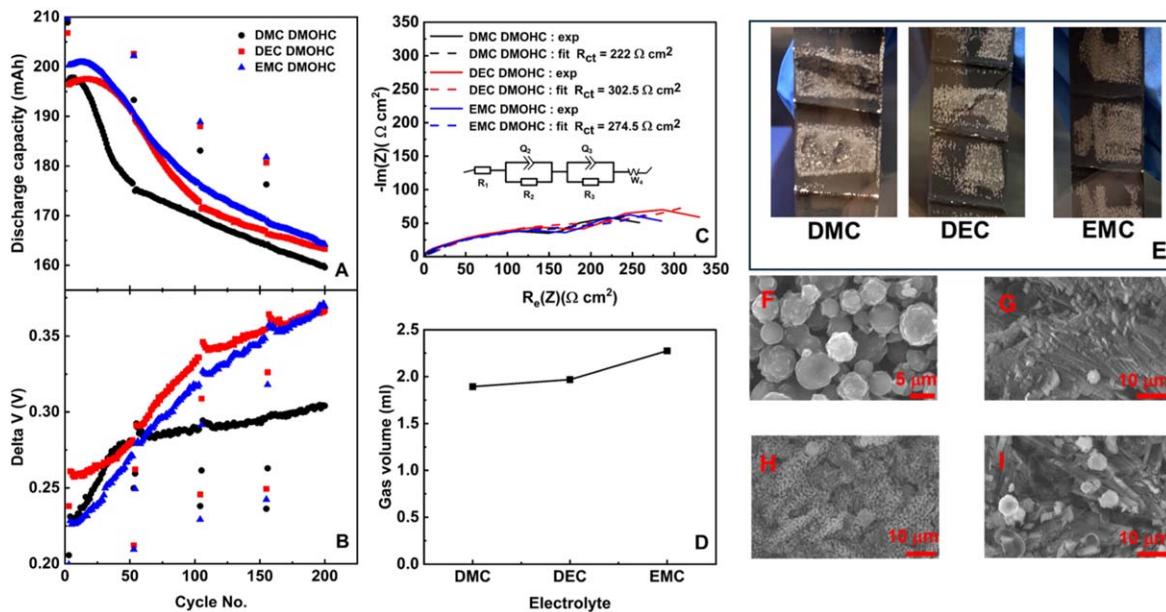


Figure 3. Evaluation of the effects of co-solvents during long-term cycling testing. (A) Discharge capacity, and (B) delta V vs cycling No. during long-term cycling between 1.5 and 4 V at 40 °C and C/3. C/20 was performed every 50 cycles. (C) The Nyquist plot after long-term cycling measured at 3.1 V and room temperature. (D) Gas evolution during long-term cycling. (E) HC anode picture with Na plating after long-term cycling. (F-I) SEM images of (F) fresh HC anode and Na plating part on the HC anodes after cycling with different co-solvents including (G) DMC, (H) DEC, and (I) EMC.

Table I. A summary of D_0 , D_1 , D_2 during 500 h storage testing.

Electrolyte	D_0 (mAh)	D_1 (mAh)	D_2 (mAh)
DMC	201	188.4	194.1
DEC	198.1	186.7	190.2
EMC	201.5	191.6	199.9

capacity retention in the DMC-containing cell, a careful examination was performed on the check-up cycling results at C/20 (Fig. 3A). A notable capacity drop, possibly due to Na inventory loss, is evident in the DMC-containing cell compared to EMC and DEC-containing cells at the C/20 cycling rate (Fig. 3A), mitigating polarization disturbances. This suggests an inferior interphase formation when DMC is used as a co-solvent, leading to increased side reactions between electrodes and electrolytes, resulting in Na inventory loss. As a common degradation product of electrolytes,^{9,18} DMOHC is unlikely to undergo decomposition and contribute to the formation of SEI and CEI. The cross reactions and carbonate transesterification between linear carbonate (e.g. DMC, DEC, EMC) and cyclic carbonate (e.g. FEC)^{19,20} are encouraged to study to understand the detailed SEI/CEI formation mechanism here. Figure 3D shows the continuous generation of a substantial amount of gas in all cells during long-term cycling.

The cycled pouch cells were then disassembled and the HC anodes were exposed to Ar in the glovebox to visually check for Na plating. Figure 3E shows photographs of the HC anodes from the pouch cells cycled with DMC, DEC, and EMC as co-solvents. Noticeably, a significant amount of Na plating is observed, potentially contributing to cell failure in this study. Ball-shaped HC particles (Fig. 3F) were observed to be embedded within plated sodium, as evidenced by thorough SEM analysis (Figs. 3G-3I).

Conclusions

In this work, we compared the effect of DMC, DEC and EMC as co-solvent with DMOHC in NCMFNZO/HC pouch cells using EIS, storage and long-term cycling testing. The electrode/electrolyte

interphase formed with DMC is inferior, leading to increased side reactions and Na inventory loss. Although EMC demonstrates improved calendar and cycling lifetime performance with some impedance control, challenges related to gas evolution and Na plating still require attention for further improvements of lifespan in SIBs.

Acknowledgments

Lin Ma at UNC Charlotte acknowledges the support by the US National Science Foundation Award No. 2301719.

ORCID

Lin Ma  <https://orcid.org/0000-0003-1183-1347>

References

1. K. Chayambuka, G. Mulder, D. L. Danilov, and P. H.-L. Notten, “Sodium-ion battery materials and electrochemical properties reviewed.” *Adv. Energy Mater.*, **8**, 1800079 (2018).
2. J.-Y. Hwang, S.-T. Myung, and Y.-K. Sun, “Sodium-ion batteries: present and future.” *Chem. Soc. Rev.*, **46**, 3529 (2017).
3. C. Bommier and X. Ji, “Electrolytes, sei formation, and binders: a review of nonelectrode factors for sodium-ion battery anodes.” *Small*, **14**, 1703576 (2018).
4. G. G. Eshetu, S. Grueon, H. Kim, S. Jeong, L. Wu, G. Gachot, S. Laruelle, M. Armand, and S. Passerini, “Comprehensive insights into the reactivity of electrolytes based on sodium ions.” *ChemSusChem*, **9**, 462 (2016).
5. X. Zhou et al., “Anion receptor weakens ClO₄⁻ solvation for high-temperature sodium-ion batteries.” *Adv. Funct. Mater.*, **34**, 2302281 (2024).
6. X. Zhao, Z. Gu, J. Guo, X. Wang, H. Liang, D. Xie, W. Li, W. Jia, and X. Wu, “Constructing bidirectional fluorine-rich electrode/electrolyte interphase via solvent redistribution toward long-term sodium battery.” *Energy & Environmental Materials*, **6**, e12474 (2023).
7. C. R. Lee, J. Byun, M. Kim, M. A. Lee, C. Hwang, J. H. Song, H. Kim, Y. Kim, J.-S. Yu, and H.-S. Kim, “Vulnerable solid electrolyte interphase deposition in sodium-ion batteries from insufficient overpotential development during formation.” *ACS Materials Letters*, **6**, 772 (2024).
8. H.-J. Liang, H.-H. Liu, X.-X. Zhao, Z.-Y. Gu, J.-L. Yang, X.-Y. Zhang, Z.-M. Liu, Y.-Z. Tang, J.-P. Zhang, and X.-L. Wu, “Electrolyte chemistry toward ultrawide-temperature (−25 to 75 °C) sodium-ion batteries achieved by phosphorus/silicon-synergistic interphase manipulation.” *J. Am. Chem. Soc.*, **146**, 7295 (2024).
9. T. Taskovic, A. Adamson, A. Clarke, E. D. Alter, A. Eldesoky, K. L. Gering, K. Tuul, and J. R. Dahn, “Alkyl dicarbonates, common electrolyte degradation

products, can enable long-lived li-ion cells at high temperatures.” *J. Electrochem. Soc.*, **170**, 090527 (2023).

10. T. Taskovic, A. Eldesoky, C. P. Aiken, and J. R. Dahn, “Low-voltage operation and lithium Bis(Fluorosulfonyl)Imide electrolyte salt enable long li-ion cell lifetimes at 85 °C.” *J. Electrochem. Soc.*, **169**, 100547 (2022).
11. J. Song, B. Xiao, Y. Lin, K. Xu, and X. Li, “Interphases in sodium-ion batteries.” *Adv. Energy Mater.*, **8**, 1703082 (2018).
12. K. Xu, “Electrolytes and interphases in li-ion batteries and beyond.” *Chem. Rev.*, **114**, 11503 (2014).
13. S. Komaba, W. Murata, T. Ishikawa, N. Yabuuchi, T. Ozeki, T. Nakayama, A. Ogata, K. Gotoh, and K. Fujiwara, “Electrochemical Na insertion and solid electrolyte interphase for hard-carbon electrodes and application to na-ion batteries.” *Adv. Funct. Mater.*, **21**, 3859 (2011).
14. H. Hijazi, Z. Ye, L. Zhang, J. Deshmukh, M. B. Johnson, J. R. Dahn, and M. Metzger, “Impact of sodium metal plating on cycling performance of layered oxide/hard carbon sodium-ion pouch cells with different voltage cut-offs.” *J. Electrochem. Soc.*, **170**, 070512 (2023).
15. V. Shipitsyn, R. Jayakumar, W. Zuo, W. Yin, E. Huber, and L. Ma, “The impact of fluoroethylene carbonate additive on charged sodium ion electrodes/electrolyte reactivity studied using accelerating rate calorimetry.” *J. Electrochem. Soc.*, **170**, 110501 (2023).
16. C. P. Aiken, J. Xia, D. Y. Wang, D. A. Stevens, S. Trussler, and J. R. Dahn, “An apparatus for the study of in situ gas evolution in li-ion pouch cells.” *J. Electrochem. Soc.*, **161**, A1548 (2014).
17. N. N. Sinha, A. J. Smith, J. C. Burns, G. Jain, K. W. Eberman, E. Scott, J. P. Gardner, and J. R. Dahn, “The use of elevated temperature storage experiments to learn about parasitic reactions in wound LiCoO_2 /graphite cells.” *J. Electrochem. Soc.*, **158**, A1194 (2011).
18. S. Wiemers-Meyer, M. Winter, and S. Nowak, “Mechanistic insights into lithium ion battery electrolyte degradation—a quantitative Nmr study.” *Phys. Chem. Chem. Phys.*, **18**, 26595 (2016).
19. S. K. Heiskanen, J. Kim, and B. L. Lucht, “Generation and evolution of the solid electrolyte interphase of lithium-ion batteries.” *Joule*, **3**, 2322 (2019).
20. C. Peschel, F. Horsthemke, M. Leißing, S. Wiemers-Meyer, J. Henschel, M. Winter, and S. Nowak, “Analysis of carbonate decomposition during solid electrolyte interphase formation in isotope-labeled lithium ion battery electrolytes: extending the knowledge about electrolyte soluble species.” *Batteries & Supercaps*, **3**, 1183 (2020).